


Environmental Science Nano

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

This critical review of the biological applications of cerium oxide nanoparticles brings together several research groups that have been working towards biomedical use of cerium oxide. The reactivity, fate and distribution of these nanomaterials in humans is critical to assessing their safety in biomedicine, given the growing evidence that this nanomaterial has potent anti-inflammatory properties.

ARTICLE

Catalytic Properties and Biomedical Applications of Cerium Oxide Nanoparticles

Cite this: DOI: 10.1039/x0xx00000x

Carl Walkey^a, Soumen Das^b, Sudipta Seal^b, Joseph Erlichman^c, Karin Heckman^c, Lina Ghibelli^d, Enrico Traversa^e, James F. McGinnis^f, and William T. Self^g,Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Cerium oxide nanoparticles (Nanoceria) have shown promise as catalytic antioxidants in the test tube, cell culture models and animal models of disease. However given the reactivity that is well established at the surface of these nanoparticles, the biological utilization of Nanoceria as a therapeutic still poses many challenges. Moreover the form that these particles take in a biological environment, such as the changes that can occur due to a protein corona, are not well established. This review aims to summarize the existing literature on biological use of Nanoceria, and to raise questions about what further study is needed to apply this interesting catalytic material to biomedical applications. These questions include: 1.) How does preparation, exposure dose, route and experimental model influence the reported effects of Nanoceria in animal studies? 2.) What are the considerations to develop Nanoceria as a therapeutic agent in regards to these parameters? 3.) What biological targets of reactive oxygen species (ROS) and reactive nitrogen species (RNS) are relevant to this targeting, and how do these properties also influence the safety of these nanomaterials?

I. Overview – Introduction and overview

Cerium oxide nanoparticles, also known as nanoceria, have been utilized for decades for applications in glass polishing and chemical mechanical polishing applications^{1, 2}. In addition, considerable interest has also arisen in the use of cerium oxide based fuel additives to reduce soot and increase efficiency of Diesel engines³. In addition the study of cerium oxide in polishing and catalysis has been well developed for a number of years, and is reviewed in other works in the *Environmental Science: Nano* Nanoceria Research themed collection. However the biological application of this rare earth oxide began in earnest around 2006 with some groundbreaking studies that showed nanoceria exhibited antioxidant character in cell culture models⁴⁻⁹.

These studies ignited an area of research that now has a larger group of scientists engaged in the study of Nanoceria for biomedical applications. A number of these scientists are authoring this report to establish a foothold on where we are in terms of biomedical applications of nanoceria, and also to set forth the challenges faced to safely and effectively use this metal oxide for biomedicine.

This critical review summarizes the findings of studies that have shown nanoceria to act in a beneficial manner in cell culture and animal studies. In addition this review emphasizes the correlation between surface chemistry of nanoceria and its catalytic properties. The surface corona is also discussed and

integrated into discussion and review of surface modifications. This review does not discuss the toxicology or toxicity of nanoceria, as this is the focus of another review in this special issue¹⁰. The discussion of surface chemistry and material science in this review is also tied closely with another review in this special issue that asks broader questions about ceria and its uses in various applications¹¹. A third closely related review discusses more of the nanoparticle aspects of cerium oxide that also relates to the catalytic nature of nanoceria that is presented in this work¹². Since these works were developed in parallel, extensive cross-referencing is made difficult and thus the reader is encouraged to seek out information in all the reviews of this special issue on nanoceria.

II. The biological identity of nanoceria

The biological behavior of a nanoparticle, including its biodistribution, pharmacokinetics, toxicity, dissolution, and elimination, depends on its physical and chemical properties. In the past, it was assumed that the properties of a nanoparticle within a biological system are the same as the properties it had following synthesis. Recently, researchers have discovered that nanoparticles interact with a diverse collection of soluble biomolecules when they enter a biological environment. Biomolecule-nanoparticle interactions lead to the formation of an adsorbed biomolecular corona^{13, 14}. The biomolecular corona changes the size, surface charge, and composition of the

nanoparticle, giving it a biological identity that is distinct from its synthetic identity¹⁵. It is the biological identity that is 'seen' by the components of a biological system¹⁶. Biomolecule-nanoparticle interactions can also change the aggregation state, activity, and dissolution characteristics of a nanoparticle. As a result, biomolecule-nanoparticle interactions within a biological environment influence a nanoparticle's biological behavior. While biomolecule-nanoparticle interactions within biofluids have been studied for a wide array of different nanoparticle types, there is a relative scarcity of research specifically considering ceria nanoparticles (nanoceria). This section briefly describes general principles governing the formation of the biological identity and its influence on downstream biological interactions. Interested readers are referred to more comprehensive reviews for a detailed discussion of this topic^{14, 15, 17}. Where appropriate, the highlighted principles are applied to the specific case of nanoceria. In the future, it may be possible to deliberately engineer the biological identity of nanoceria to maximize efficacy and safety, enable new applications, and speed clinical translation. Although the biomolecular corona typically consists of proteins, lipids, sugars, and small molecules, the remainder of this section will focus on protein-nanoparticle interactions because they hold particular biological significance and are the most widely studied.

Formation of the biological identity of nanoceria. Biofluids typically contain diverse collections of soluble proteins. Blood plasma, for example, contains over 3700 unique proteins, varying in abundance by over 10 orders of magnitude¹⁸. When a nanoparticle enters a biofluid, proteins begin migrating towards its surface. The most abundant proteins will, on average, arrive first. Often, the most abundant proteins associate weakly with the nanoparticle surface, desorb rapidly and return to solution. Over time, proteins with lower abundance but higher affinity replace proteins with high abundance but low affinity^{19, 20}. Although there is no fixed time period over which the exchange process takes place, the protein corona around many nanoparticle formulations reaches a quasi-equilibrium state within minutes^{21, 22}. Because the nanoparticle surface tends to enrich low abundance proteins, the relative abundance of proteins in the adsorbed protein corona does not, in general, follow the relative abundance of the same proteins in the biofluid^{23, 24}. This has led to the somewhat unexpected observation that the most abundant protein in blood plasma, serum albumin, is found at low abundance within the protein corona around most nanoparticle formulations^{15, 25}. Although it has not yet been established experimentally, the protein corona around nanoceria will presumably enrich low abundance proteins.

Proteins within the protein corona are conceptually divided into two classes depending on their adsorption affinity^{13, 24}. Proteins within the 'hard' corona are strongly-bound and remain associated with the nanoparticle for minutes or hours. Proteins within the 'soft' corona, in contrast, form a dynamic

equilibrium with the nanoparticle and rapidly desorb when the biofluid is removed. Casals et al. observed that, over a time period spanning days, the protein corona around nanoceria exposed to fetal bovine serum evolved from a dynamic reversible state to an irreversible state. The authors referred to this process as hardening^{26, 27}. Hardening of the protein corona may be a result of changes in the conformation and orientation of adsorbed proteins.

Because of their prolonged residence time, proteins within the hard corona remain associated with the nanoparticle as it interacts with components of the biological system, including cells. The hard corona thus defines, in part or in whole, the bioactive interface of a nanoparticle in a biological environment, while the soft corona is thought to play a less important role.

Since the hard corona can be isolated from the surrounding biological environment, and given its importance in mediating the biological response, its composition is relatively well characterized. A priori, it is unclear which of the hundreds or thousands of distinct proteins within a biofluid will be incorporated in the hard protein corona around a given nanoparticle formulation. To characterize the composition of the hard protein corona, researchers are relying increasingly on modern quantitative mass spectrometry techniques adapted from the field of proteomics^{22, 28, 29}. These techniques are capable of simultaneously identifying and quantifying the relative abundance of proteins within a complex sample by rapidly sequencing peptide fragments generated by proteolysis. Given the prevalence of intravenous injection as a route of nanoparticle administration, the majority of researchers have characterized the composition of the protein corona following exposure to isolated blood plasma or serum. The plasma protein corona around a wide range of distinct nanoparticles including carbon nanotubes³⁰, metal oxide nanoparticles³¹, polymer nanoparticles²³, liposomes³², silica nanoparticles²⁴, and gold nanoparticles³³ has been extensively characterized. These studies have shown that the plasma protein corona is complex, routinely consisting of dozens of distinct proteins spanning orders of magnitude in relative abundance^{14, 15}. Adsorbed plasma proteins tend to be involved in complement activation, coagulation, opsonization, acute phase responses, and inflammation. However, there is no 'universal' plasma protein corona formed around all nanoparticles. Instead, the identities and relative abundances of the adsorbed proteins depend on the nanoparticle composition, size, shape, and surface modification. At the time of writing, no detailed proteomic studies characterizing the plasma protein corona around nanoceria have been published.

It has been widely reported that irrespective of the surface charge of a nanoparticle following synthesis, it acquires a negative surface charge after being incubated in blood plasma^{21, 33, 34}. When proteins adsorb to the surface of a nanoparticle, the charge of the nanoparticle reflects the charge of the

adsorbed proteins, not the underlying synthesized nanoparticle surface. Because proteins in plasma tend to carry a net negative charge at physiological pH, their adsorption imparts a negative charge to the nanoparticle. Even nanoparticles with cationic surfaces after synthesis undergo a charge reversal upon incubation in blood plasma³⁵. This observation calls into question the long-standing belief that cationic nanoceria associate with cells by interacting electrostatically with anionic cell-surface glycoproteins.

Upon exposure to a biofluid, protein-nanoparticle interactions may induce nanoparticle aggregation or promote colloidal stability³⁶. The adsorption of large, bulky, and hydrophilic proteins, such as serum albumin, has been shown to stabilize nanoparticles against aggregation by sterically inhibiting direct nanoparticle contact, whereas the adsorption of smaller proteins that are more hydrophobic or those that carry a charge that is opposed to the that of the nanoparticles tends to promote aggregation^{37,38}. Protein-nanoparticle interactions can also act to pull apart nanoparticles that are aggregated upon entering a biofluid. Protein-nanoparticle interactions may have a significant influence on the aggregation state of nanoceria within biofluids given that most preparations are aggregated after synthesis³⁹. Biomolecule interactions within the environment may also alter nanoceria stability, altering its availability and ecotoxicity⁴⁰.

Influence of the biological identity on the biological response to nanoceria. The mechanism of interaction between nanoparticles and cells, along with the resulting cellular response is typically studied using *in vitro* cell culture systems. Studies have shown that the presence of serum proteins in the cell culture media decreases the association of carbon nanotubes⁴¹, titanium dioxide nanoparticles³⁹, silica nanoparticles⁴², polystyrene nanoparticles⁴³, quantum dots⁴⁴, gold nanoparticles⁴⁴, and graphene oxide nanosheets⁴⁵ with multiple cell types from distinct tissue sources. Lesniak et al. suggest that, in the absence of serum proteins, nanoparticles with high surface activity interact strongly with biomolecules within the cell membrane, which promotes cell association and uptake⁴⁶. When serum is present in the culture media, adsorbed serum proteins 'passivate' the nanoparticle surface, rendering it hydrophilic and creating a steric shield that inhibits direct interactions between the cell membrane and the underlying nanoparticle surface.

The passivation of a nanoparticle's surface by adsorbed serum proteins can also inhibit physical damage to the cell membrane and cell-surface biomolecules that results in cytotoxicity⁴⁷. It has been suggested that the formation of an artificial biomolecular corona may be used as a means of 'detoxifying' nanoparticle formulations, including nanoceria, prior to use in medical applications or disposal and release in the environment⁴⁸. However, this approach must be taken with care, since degradation or loss of the protective coating could restore the toxicity of the formulations⁴⁹.

While the formation of a protein corona may suppress non-specific interactions between the pristine nanoparticle surface and the cell surface, specific interactions between cell-surface receptors and adsorbed proteins are also possible. The adsorption of plasma protein opsonins, in particular immunoglobulins and some complement factors, makes nanoparticles more 'visible' to tissue-resident macrophages in the liver and spleen⁵⁰⁻⁵². Macrophages selectively express opsonin receptors including Fc and complement receptors that recognize surface-adsorbed opsonins, leading to efficient nanoparticle uptake⁵³. Opsonin adsorption and induced aggregation upon exposure to blood plasma are considered two of the most important causes of the rapid clearance of nanoparticles from the blood following intravenous administration⁵⁴.

Designing nanoceria with controlled biological identities and biological responses. The physical and chemical properties of a nanoparticle determine the nature of protein-nanoparticle interactions within a biofluid and the composition and structure of the protein corona. This is because the propensity of a nanoparticle to engage in interactions with specific amino acid side chains will determine the relative protein affinities⁵⁵. Changes in the charge, hydrophobicity, and chemical structure of a nanoparticle's surface will thus influence the composition of the resulting protein corona. For example, acidic carboxy-functionalized polystyrene nanoparticles preferentially adsorb basic proteins (pI > 5.5) from plasma, whereas amine-functionalized polystyrene nanoparticles preferentially adsorb acidic proteins (pI < 5.5)⁵⁶. It is likely that changes in the physical and chemical properties of nanoceria will influence the composition and structure of the resulting protein corona.

Nanoparticle size influences lateral interactions between adjacent adsorbed proteins and the local geometry and structure of the protein binding sites on a nanoparticle. As such, the interaction of biomolecules with nanoparticles tends to be distinct from the interaction of biomolecules with 'bulk' materials with the same composition²⁸. However, there are no obvious correlations between protein molecular weight, isoelectric point, and the trend in relative adsorption between nanoparticle sizes. It is likely that the effect of nanoparticle size on the adsorbed abundance of individual proteins is a complex function of protein size, shape, amino acid composition, and 3D structure. Yet, it appears that the effect of nanoparticle size becomes significant only when it approaches the size of the protein, which typically occurs in the ~<30nm range^{29, 57, 58}. Since nanoceria formulations are in the sub-10 nm range, changes in nanoceria size are expected to influence the composition of the protein corona.

The adsorbed surface stabilizers that are incorporated either synthetically or post-synthetically influence the surface

chemistry of a nanoparticle. As such, a given nanoparticle core with a specific geometry, chemical composition, and crystallinity has a range of possible protein coronae, depending on the chemistry, structure, and surface arrangement of the associated surface stabilizers. Rational design of the surface stabilizing molecules is one method that can be used to control protein-nanoparticle interactions and thus the biological behavior of a nanoparticle. Because uncontrolled protein adsorption can often lead to detrimental effects, such as the rapid clearance of nanoparticles by tissue-resident macrophages of the liver and spleen, surface modification strategies have been developed with the goal of altogether eliminating protein adsorption. One of the most popular strategies is to graft the surface of a nanoparticle with long chains of the hydrophilic and conformationally-flexible polymer poly(ethylene glycol) (PEG)⁵⁹. PEG grafting prevents protein adsorption by blocking protein-binding sites and creating a steric barrier that prevents protein diffusion to the nanoparticle surface⁶⁰. While PEG grafting is effective at reducing plasma protein adsorption and macrophage uptake, and hence increasing blood half-life, it also reduces interactions with target cells, which can lower target-site localization^{29, 61, 62}.

Instead of designing the surface of a nanoparticle to eliminate protein adsorption, it may instead be designed to selectively adsorb specific plasma proteins that promote target site localization. Using nanoceria as a reactive oxygen species scavenger for the treatment of neurodegenerative diseases is one of its most promising therapeutic applications. The delivery of functional nanoceria to the brain is a prerequisite for such applications, but is also a significant technical challenge. If nanoceria are administered intravenously, they must not only evade capture by tissue-resident macrophages, but must also cross the layer of endothelial cells that comprises the blood-brain barrier (BBB). Studies have shown that coating polymer nanoparticles with polysorbate 80 can significantly enhance their transport across the BBB⁶³. Adsorbed polysorbate 80 promotes the selective adsorption of apolipoproteins B and E to the nanoparticle surface, which facilitate transcytosis by interacting with lipoprotein receptors expressed on the surface of BBB endothelial cells^{64, 65}. Surface-modifying nanoceria to selectively adsorb apolipoproteins B and E from blood plasma may also facilitate their transport across the BBB. However, it is not yet clear whether polysorbate 80 modification of nanoceria will promote the adsorption of apolipoproteins B and E.

The importance of protein-nanoparticle interactions in the fields of nanomedicine and nanotoxicity has begun to emerge, suggesting a critical role of the protein 'corona' in mediating the biological effects of nanoparticles. Development of the corona is a dynamic, two-step process that results in the evolution of a stable, 'hard corona' and a more labile 'soft corona'. The cellular effects of the protein-nanoparticle interface are diverse and have only recently been studied in simplified biological systems. The effects of protein binding

include cell membrane receptor activation and altered routes of endocytosis and cellular trafficking. The nature of this protein mantle is dictated by the size, composition and surface properties of the nanoparticle. The astounding divergence in the abundance and nature of proteins comprising this layer has been described with only very modest changes in physico-chemical attributes⁶⁶. Given the complexity of these interactions, a formidable task lies ahead in understanding the nature of these interactions, predicting the biological outcome of nanoparticle-protein interactions and studying these effects in intact, living systems. This is particularly relevant for harnessing the potential of nanoceria in biological applications. The inherent ability of nanoceria to participate in redox-coupled reactions reflects their significant surface reactivity. The adsorption of proteins to nanoceria may reduce its catalytic potential but, more importantly, may alter the conformation of proteins bound to the particle, exposing novel biological epitopes that may drive downstream cellular effects not normally associated with the native protein. Gaining insight into the nature of these complex interactions is critical for the rational design of nanoceria in the future.

III. Cerium oxide nanoparticles act as biological mimics of enzymes involved in oxidative stress defense

Cerium oxide nanoparticles (Nanoceria) act as superoxide dismutase mimetics. Superoxide ($O_2^{\bullet-}$), the product of a one electron reduction of the dioxygen diradical (O_2), is a key reactive oxygen species in biological systems⁶⁷. It is generated as a by-product of a number of metabolic processes such as the respiratory chain in the mitochondria as well as enzymes such as xanthine oxidase⁶⁸. Although it can spontaneously decompose into hydrogen peroxide, it also can react with other radicals such as the nitric oxide radical ($\bullet NO$) to generate other oxidants including peroxynitrite ($ONOO^-$). Because of these reactions, mammals and many microbes produce catalysts to limit the steady state concentration of superoxide in the cell, primarily superoxide dismutases and superoxide reductases⁶⁹. However during inflammation, the production of superoxide can overwhelm these defenses leading to increased reactive oxygen species (ROS) and reactive nitrogen species (RNS). Thus keeping superoxide levels in check is a key determinant in the limitation of inflammation.

Nanoceria were first shown to be superoxide dismutase (SOD) mimetics by Korsvik et al.⁷⁰ in 2007. In this report two preparations of Nanoceria were studied – one with very few cerium atoms in the +3 oxidation state at the surface and a second material with higher levels of cerium atoms in the +3 oxidation state based on X-ray photoelectron spectroscopy (XPS) analysis. This was the first report of a catalytic activity for this material under biologically relevant conditions (aqueous buffered near neutrality). Indeed it also established an important parameter – that the synthesis of the nanoparticles and the surface chemical properties of this material can make a significant difference in terms of catalytic activity of the material. A follow up study focused on further analysis of this

surface chemistry revealed that the nanoparticles with higher amounts of cerium atoms in the +3 oxidation state at the surface could be altered by excess hydrogen peroxide to revert to a surface chemistry with lower levels of this reduced state⁷¹. In line with Korsvik et al., this change in surface chemistry also correlated with a reduction in the SOD mimetic activity.

The impact of PEGylation on the SOD mimetic activity by nanoceria. The first study to address the generation of a biocompatible surface of cerium oxide utilized polyethylene glycol polymers (PEGylation). The presence of PEG on the surface of the Nanoceria did not prevent SOD mimetic activity, and the level of cerium in the +3 oxidation state again correlated well with the SOD mimetic activity⁷². However the extent of PEG coverage may alter the reactivity of the surface depending on the synthesis procedures used to make the Nanoceria. Another attempt to make Nanoceria more stable was reported in 2012 using poly(lactic-co-glycolic acid) (PLGA)⁷³. The PLGA coated Nanoceria retained SOD mimetic activity for a longer period of time (90 days) after synthesis, a process known as ‘aging’. The precise changes and the mechanism of these changes that occur during aging are not well understood. In addition to surface changes for biomaterial applications, another report showed that phosphate ions could also shift the surface oxidation state of Nanoceria and result in changes in SOD mimetic activity⁷⁴. This study presumed that the phosphate ions are binding in or near oxygen vacancies that are predicted to lead to reduced cerium atoms at the surface, although it should be noted that phosphate binding to other cerium oxide nanoparticles may or may not affect their catalytic activities depending on the presence of stabilizing groups. Recent work showed that phosphate ions are binding on ceria nanoparticles enriched in the +3 oxidation state while they do not adsorb when Ce is mostly in the +4 valence state⁷⁵.

Evidence for SOD mimetic activity *in vivo*.

Estevez et al. demonstrated in an ischemic brain slice model that cerium oxide nanoparticles exhibited potent SOD mimetic activity⁷⁶. A more recent report by Ganesana et al. studied SOD mimetic activity of Nanoceria in a brain slice model and demonstrated that administration of Nanoceria did lead to reduction in the superoxide levels in this *ex vivo* system. In this study the authors were able to show that 5 micromolar levels of Nanoceria is equivalent to 580 units of SOD activity – a remarkable level of catalytic activity in this model⁷⁷. This key finding indicates that under biologically relevant conditions Nanoceria do exhibit SOD mimetic activity⁷⁷. Thus all these reports have validated the initial report that Nanoceria can exhibit SOD mimetic activity by a variety of assay systems and also show that this activity is likely occurring *in vivo*. Studies that tie this activity to efficacy of Nanoceria are not discussed here but are discussed elsewhere in this article and compendium.

Although there are significant amounts of wet chemistry data that correlate the SOD mimetic activity with surface chemistry and material synthesis, the core reaction mechanism is still not

well understood. A recent study that used a combination of molecular dynamics (MD) and density functional theory (DFT) alongside wet chemical measurements has shed some light on the reactivity of Nanoceria with superoxide⁷⁸. In this study, the presence of water on the surface of Nanoceria was investigated and the results suggest that cerium oxide that is synthesized in water contains reactive regions that are altered upon dehydration. To confirm these predictions, water based Nanoceria were synthesized and shown to have SOD mimetic activity only prior to dehydration. Removal of water from this preparation significantly reduced the SOD mimetic activity of the nanoparticles. This study can lead to future work to better understand the mechanism of superoxide dismutase activity of Nanoceria.

Nanoceria display catalase mimetic activity. Pirmohamed et al. have also described the catalase mimetic activity of Nanoceria⁷¹. Several classes of enzymes are involved in the modulation of hydrogen peroxide levels in mammals, including catalase, glutathione peroxidases and peroxiredoxins. The overall catalytically weak activity of Nanoceria as compared to the highly efficient catalyst catalase initially suggested this activity might not be relevant *in vivo*⁷⁹. However studies have shown that peroxides are likely the most stable and abundant ROS *in vivo*, and thus a catalyst that can reduce peroxide levels could prove critical during inflammation or to prevent metal catalyzed oxidation reactions (Fenton reactions) from occurring. However the role that peroxides play in biology is growing, and the level of peroxides is modulated by a number of enzymes (glutathione peroxidases, peroxiredoxins, catalase), many of which require reducing potential in the form of thioredoxin and glutaredoxin⁸⁰.

Moreover the catalase mimetic activity of Nanoceria is inversely related to the SOD mimetic activity in terms of the surface charge of cerium. In other words, when the concentration of cerium atoms at the surface of the nanoparticle in the +3 oxidation state are more abundant, the catalase mimetic activity is weak⁷⁹. It was in this initial study that we stumbled upon (by accident) the effect of phosphate ions on these activities. A follow up study showed that phosphate can interconvert Nanoceria from SOD to catalase mimetics *in vitro*, correlating with cerium reduction state⁷⁴. This suggests overall that reduced cerium sites, i.e. oxygen vacancies, do not contribute to catalase mimetic activity and thus reduce the overall reactivity of the nanoparticle. This also indicates that, given that the level of phosphate in most biological systems is in the millimolar range, the reactivity of nanoceria with phosphate must be taken into account when correlating chemical reactions in a test tube to chemistry occurring *in vivo*. In contrast, a very recent report by Vicki Colvin’s group has shown that Nanoceria produced by an alternate method (not water based) are good catalase mimetics, and the authors of this study suggest that oxygen vacancies are critical to the reactivity with hydrogen peroxide⁸¹. In addition the authors found that when coated with oleic acid, these Nanoceria were quite stable

over a long period of time and were more robust as catalysts in successive reactions. This adds to our understanding of CeNP stability and the properties resulting from synthesis, but will also lead to renewed efforts to understand the catalysis that is occurring at the surface as well. Another study has shown that aqueous Nanoceria have both SOD mimetic and catalase mimetic *in vivo*⁸². It should also be noted that some groups have questioned the presence of cerium in the 3+ oxidation state⁸³, thus given the disparity in the results of several studies there is likely an underlying mechanism that has yet to be elucidated.

Evidence for scavenging of nitric oxide radical. The first report that conclusively demonstrated the scavenging of reactive nitrogen species is that of Estevez et al.⁷⁶. This study was done in an intact brain tissue that generated reactive oxygen and nitrogen species *in vitro*, and thus it is clear that Nanoceria can directly affect (reduce) RNS *in vivo*. In parallel work *in vitro*, Dowding et al. investigated whether Nanoceria could react with biologically relevant reactive nitrogen species. The radical gas nitric oxide ($\bullet\text{NO}$) can be followed by a number of techniques and can be generated by a series of chemicals known as NONOates. Dowding measured the level of nitric oxide generated from NONOates using two independent methods⁸⁴, and followed the reaction of nitric oxide with the ferrous form of hemoglobin. This study found that in the presence of Nanoceria with a low level of cerium in the +3 oxidation state, the Nanoceria could prevent the interaction with ferrous hemoglobin in a dose dependent manner⁸⁴. This indicated that nitric oxide was interacting with Nanoceria. An alternate NONOate was also tested by an alternate method to follow nitric oxide, a copper fluorescein complex. Again the presence of Nanoceria with lower levels of cerium in the +3 oxidation state reduced the reaction of NO with the copper complex, indicating a reactivity with Nanoceria⁸⁴. In both cases positive controls such as glutathione or a radical scavenger (DEPMPO) were also shown to compete. These results suggest strongly that Nanoceria can scavenge nitric oxide. Because the level of nitric oxide is difficult to follow *in vitro*, the kinetics of this reaction has not yet been established.

Nanoceria accelerate the decay of peroxyntirite. Peroxyntirite (ONOO-) is a strong oxidizing agent that is formed primarily from the reaction of superoxide and nitric oxide radicals⁸⁵. Given the significant reduction in nitrotyrosine levels (about 70%) observed by Estevez⁷⁶, the possibility that Nanoceria reacted with peroxyntirite was raised. This potent oxidant and nitrating species is stable under basic conditions, yet spontaneously decomposes at neutral or near neutral pH. This allowed for the reaction of peroxyntirite in a controlled (pH dependent) fashion with nanoceria⁸⁶. Dowding observed a significant increase in the decay of peroxyntirite when Nanoceria were present in a buffered reaction near physiological pH levels⁸⁷. A comparable peroxyntirite scavenger, uric acid, was needed in millimolar levels to show the same accelerated decay (**Figure 1**). Thus it is likely that

Nanoceria are potent reactants with peroxyntirite *in vivo*, yet this is difficult at best to study *in vitro*, given the cadre of end products that occur upon peroxyntirite decay⁸⁵. The boronate probe used to follow peroxyntirite levels have been shown to be preferentially detecting peroxyntirite⁸⁷. Nanoceria were also shown to reduce 3-nitrotyrosine levels in proteins when exposed to peroxyntirite in a test tube⁸⁷, mirroring the results obtained *in vitro*⁷⁶. This indicates by a variety of methods that Nanoceria are reacting with peroxyntirite directly or one of its many radical end products during decomposition, such as the carbonate radical⁸⁵.

Given the wide distribution of the types of nanoceria, and the differences observed in catalytic activity, a summary of a wide range of studies in which the surface chemistry of nanoceria has been combined with the study of catalysis is listed in Table S1 (ESI). This table enables a comparison of the types of nanoceria synthesis method, nanoceria catalysis and references the study from which the data are derived. Albeit not all inclusive, this can give the reader a guide to the kinds of correlations that have been observed for surface chemistry analysis and catalytic activities.

IV. Uptake and Distribution of cerium oxide using *in vitro* cell culture models and *in vivo* models

Redox active cerium oxide nanoparticles (Nanoceria) can scavenge reactive oxygen (ROS) as well as reactive nitrogen species (RNS). It is interesting to mention that the regenerative nature of Nanoceria's surface make these nanoparticles different from other known antioxidant molecules. Different bio-medical applications of Nanoceria that have been explored in the last few years include inhibition of neovascular macular degeneration⁸⁸⁻⁹⁰, protection against laser induced eye damage⁵, protection against radiation induced tissue damage^{4, 91, 92}, induction of pro-angiogenesis and wound healing⁹³⁻⁹⁶, management of ischemic stroke, neurodegenerative diseases^{9, 97-100}, anti-angiogenesis and inhibition of tumor stroma interaction¹⁰¹⁻¹⁰⁴. These studies, using both *in vitro* and *in vivo* models, have shown that Nanoceria have the potential to be developed as a therapeutic agent for a wide range of pathologies associated with oxidative injury.

Subcellular localization of nanoceria. Nanoparticles' cellular interaction, cellular uptake and subcellular localization are determined by physical properties of the nanoparticles which include nanoparticles' size/agglomeration status in media, surface charge, and residual surfactant/presence of functional group/coating on the surface of the nanoparticles. Negatively charged nanoceria particles were taken up effectively in a cell culture model (A549) in one of the first studies to address uptake¹⁰⁵. These nanoceria were bare, but the potential for difference in uptake in cells based on surface bound chemicals (ions, lipids, proteins, protein corona) likely can alter uptake efficiency and the mechanism(s) of uptake. Residual hexamethylenetetramine (HMT) on the surface of the nanoceria

not only changes the catalytic property of the nanoparticles (increased phosphatase activity, and loss of SOD and catalase mimetic activity), but also led to increases in the cellular uptake (HUVEC cell culture). Higher surface charge nanoparticles nanoceria2 (30.2 mV) and HMT-nanoceria (34.6 mV) were found to be taken up with greater efficiency as compared to nanoceria1 (18 mV). Moreover, cellular uptake of HMT-nanoceria was two fold higher compared to nanoceria2, which suggests that the presence of a functional group/stabilizer can influence nanoparticle-cell interaction and therefore cellular uptake⁸⁶. In our previous study we have shown that for nanoceria1 and nanoceria2 after incubation in HUVEC cell culture medium both show $\sim(-)9\text{mV}$ surface charge⁹³, therefore differential cellular uptake may be due to difference in physicochemical properties. In particular, presence of functional groups/molecule on the surface of the nanoparticles can have greater influence on nanoparticle-cell interaction than surface charge, which may explain different trend in the uptake observed in these two studies.^{86, 105} Moreover, two different cell lines used in these studies cannot be ignored. Since these nanoceria were made in different ways this emphasizes influences of the variability of the nanoparticles physicochemical properties in biological systems.

The cellular uptake mechanism of nanoceria has also been studied using carboxy-fluorescence conjugated nanoceria (F-nanoceria). Energy dependent, clathrin and caveolae-mediated endocytosis was reported for the cellular uptake of F-nanoceria. F-nanoceria were observed localized in lysosomes, the endoplasmic reticulum and mitochondria, in addition to the cytoplasm and nucleus¹⁰⁶. The presence of nanoceria in all major subcellular compartments ensures protection against a variety of oxidative stresses. However it should be noted that the behavior of bare nanoceria as compared to that conjugated with a dye is likely quite different.

Cerium oxide bio-distribution and route of administration.

The route of administration of the nanoparticles is another important parameter to assess in delivering materials to particular target organs. achieve maximum benefits of nanoceria. In-vivo real time imaging revealed that intravenous injection of F-nanoceria deposited in liver within 3 h of injection. Moreover, F-nanoceria were mainly found deposited in the liver, spleen and lungs and persisted 2 weeks after F-nanoceria injection.

To examine bio-distribution of bare nanoceria, 0.5 mg/kg of body weight of nanoceria (once in a week) were administered in three different routes, perorally (PO), intravenously (IV), or intraperitoneally (IP) for two and five weeks. IV administration resulted in the greatest tissue deposition (liver, kidney, heart, brain, spleen and lung) of Nanoceria, followed by the IP and PO routes, results that were quantified using inductively coupled plasma mass spectroscopy. For IV and IP routes, nanoceria mainly deposited in the spleen and liver whereas very low amounts were found in the lungs and kidneys. It is important to mention that this specific formulation of nanoceria was not found in heart or brain. Nanoceria administered in PO

route showed minimal organ deposition. Tissue accumulation was highest following IV administration. Multiple weekly systemic injections of nanoceria over a period of 5 weeks did not show any overt pathology in different organs¹⁰⁷.

On the other hand citric acid coated Nanoceria showed different tissue distribution and in addition to spleen and liver citric acid Nanoceria were also found in brain when injected through IV route. Citric acid coated Nanoceria are reported to have increased blood circulation time. Citric acid Nanoceria were even found in blood circulation after 30 days of administration, and as expected, longer blood circulation times were observed for smaller nanoparticles (5-nm) as compared to larger Nanoceria (55-nm)¹⁰⁸. Therefore, bio-distribution and pharmacokinetics data of the nanoparticles will help to select Nanoceria formulation for specific application.

V. Mechanistic studies on the cell effects of nanoceria

The bio-effects of nanoceria are generally attributed to the $\text{Ce}^{3+}/\text{Ce}^{4+}$ redox switch¹⁰⁹. The oxygen vacancies may also theoretically exert a biological activity of their own, i.e., independently of the redox cycle. Modifications of the materials through nanoceria doping with Sm, which consists in the substitution of Sm that has a fix 3+ valence in the Ce lattice sites, ends up in eliminating the redox switch activity and in decreasing the Ce^{3+} concentration, thereby keeping the number of oxygen vacancies almost constant. The comparison of the effects exerted by nanoceria and Sm-doped nanoceria allows discriminating the eventual roles played by oxygen vacancies or the $\text{Ce}^{3+}/\text{Ce}^{4+}$ redox couple. With this approach, it was possible to demonstrate that the antioxidant and antiapoptotic activity of nanoceria in a system of human monocytes are due to the redox activity of nanoceria, since they were abolished by Sm-doping¹¹⁰. It is uncertain whether oxygen vacancies possess biological activity, and so far none has been described.

Nanoceria was shown to increase cell survival in conditions of stress by inhibiting apoptosis¹⁰⁹. Apoptosis is often a consequence of oxidative stress, therefore it is conceivable that anti-oxidant agents such as nanoceria, decreasing the insult, increase cell survival. This was demonstrated in a study on U937 cells, where oxidative vs. non-oxidative apoptosis can be recognized by a different cell morphology¹¹¹. Nanoceria was shown to inhibit only oxidative apoptosis, whereas the non-oxidative pathway remains unaffected¹¹⁰. In the search for the mechanism at the basis of this effect, it was observed that the depletion of glutathione (the main intracellular antioxidant), a phenomenon that is a hallmark of stress-induced apoptosis¹¹², is prevented by nanoceria¹¹⁰, suggesting that nanoceria may act on glutathione metabolism, and specifically on its transporters, which are protein complexes present on the cell membrane that allow the export of glutathione outside cells, and are redox-regulated proteins¹¹³. Recently the antioxidant and cell protective action of nanoceria was confirmed in a cell inflammatory model, where it is shown that nanoceria protect from alterations in oxidative metabolism induced by the cytotoxic agent tumor necrosis factor (TNF α) [new ref:

Nanoceria protects from alterations in oxidative metabolism and calcium overloads induced by TNF α and cycloheximide in U937 cells¹¹⁴.

Nanoceria were shown to affect endogenous cell defenses, modulating the activity of redox-sensitive nuclear transcription factors such as nuclear factor-kappa B (NF- κ B)^{91, 115, 116} and activator protein 1 (AP1)⁹¹, which are devoted to the promotion of cell survival pathways. Moreover, nanoceria increase the expression of superoxide dismutase, thereby ameliorating the ROS scavenging effect in response to ionizing radiation^{91, 115}. Nanoceria possess anti-inflammatory ability by inhibiting NF- κ B activation, thereby reducing the expression of the downstream pro-inflammatory proteins¹¹⁶⁻¹¹⁸, such as inducible nitric oxide synthase (iNOS) and the pro-inflammatory cytokines produced by stimulated macrophages^{117, 119}.

Several studies show that nanoceria selectively protect from damage normal but not cancer cells; in fact, in cancer cells nanoceria is even pro-apoptotic^{91, 115}. These findings are of paramount importance, because to date no agents that are selectively toxic for cancer cells have been found.

It was hypothesized that the selective toxicity of nanoceria against cancer cells is due to the inhibition of nanoceria catalase-like activity occurring in acidic (pH 4.3) environments¹²⁰: the hypothesis is based on the assumption that pH of cancer microenvironment is acidic due to the Warburg effect⁹¹. Moreover, the pH-dependent inhibition of catalase might play a role in the selective toxicity of nanoceria on tumor cells considering the very acidic pH (~ 4) present within the lysosomal cell compartment¹²¹. Interestingly, it is shown that the cytosolic localization of nanoceria is different in normal vs. cancer cells, being cytosolic vs. lysosomal, respectively. Internalization of the same preparation of nanoceria vary in tumor vs. normal cells, being localized in lysosomes vs. cytosol, respectively¹²¹. Future research will undoubtedly focus on the reason why tumor vs. normal cells impart a different localization to nanoceria¹²².

Cerium oxide nanoparticles protect cells from ionizing radiations¹¹⁵. However, in some instances irradiated nanoceria behave as pro-oxidant agents. Indeed, it was shown that specific intensities of X-rays, peaking at 50-60 keV, induce the production of reactive oxygen species¹²³. At the same time, the Ce³⁺/Ce⁴⁺ redox couple on nanoceria surface scavenges the reactive oxygen species produced by irradiation, and therefore the resulting effects depend on the balance between these two opposite mechanisms⁹¹.

Oxidative stress has important implications in cardiovascular diseases as their reason and/or consequence¹²⁴. Cardiac progenitor cells are promising as source for autologous tissue engineering for cardiac repair¹²⁵. ROS are paramount for reducing stem cell lifetime, inducing senescence¹²⁶, and impairing self-renewal¹²⁷. Nanoceria may counteract these effects¹²⁸. Thus, the internalized nanoparticles worked as a potent, long-lasting ROS scavenger able to protect cells from the oxidative damage.

In the near future, much effort will be devoted to: i) elucidate the cellular mechanisms behind the action of cerium oxide as a function of the cell type; ii) understand the interactions between this promising material and cells; iii) understand the peculiar differential effects nanoceria exert on tumor vs. normal cells, with the goal of proposing novel approaches to cancer therapy; iv) to implement the studies on the effects of nanoceria in the improvement of tissue engineering.

VI. Traversing Physiological Barriers: Differences in Biological Test Beds

Most studies using nanoceria over the past decade have examined biological effects using reduced, *in vitro* preparations that do not fully recapitulate *in vivo* interactions^{4, 6-9, 91, 117}. Most often, *in vitro* approaches have made use of immortalized cell lines that differ in their genetic and phenotypic profile compared to endogenous, native cells. The principle advantage of *in vitro* studies is the ability to make detailed, single cell measurements of primary cell cultures or tissues slices that retain intact architecture and more accurately reflect cellular function of native tissues. However, these preparations may not be ideal as there are fewer barriers between the bulk solution and cellular uptake of the particles compared to *in vivo* models that have many more anatomical barriers that must be overcome for nanoceria to reach a biological target. For example, particles entering the lung or gastrointestinal tract destined for the blood stream would need to traverse at least ten separate biological barriers before reaching their target¹²⁹, and the number of barriers could exceed fifteen if the target cell were a neuron (depending on the route of delivery). At each barrier, the nanoparticle would encounter cell membranes that may vary in their composition as a function of their polarity (i.e. apical and basolateral membranes) and the tortuosity of paracellular fluid movement through tissue or uptake by mobile cell types (immune cells). As the nanoceria transitions across barriers, the fluid compartments it encounters will also vary in their ionic strength, pH and protein content, all of which can profoundly influence both the physical and chemical attributes of the particle and hence its biological activity.

Importance of Nanoparticle Stabilizers

To date, studies exploring the therapeutic potential of nanoceria using intact animals are limited^{89, 91, 100, 130}, and most investigators have utilized nanoceria ranging in size from 3 to 55 nm, often with very negative zeta potentials (< -50 mV; with the exception of the eye) administered as spherical, nanodispersions of bare ceria particles or nominally stabilized with citrate or polyethylene glycol^{100, 108}. In rodent models, bare particles have very short plasma half-lives and are prone to aggregation and accumulation in reticuloendothelial organs^{89, 108, 131}. Indeed, non-stabilized nanoparticles frequently bind complement or other proteins that lead to rapid removal of the nanomaterial by circulating and tissue resident macrophages^{29, 132}. Commercially available, unstabilized or citrate-stabilized cerium oxide nanoparticles deposit in the highest levels in the

spleen and liver in rodents^{89, 108, 131, 133, 134}. Delivery of non-stabilized, 3-5 nm particles (cumulative dose 2.5 mg/kg) over a 5 week period resulted in ceria deposition of > 20,000 ug/g in the liver and spleen one week after the final injection¹⁰⁷. In contrast, single injections of 5 nm (85 mg/kg) or 30 nm (70 mg/kg) citrate-stabilized nanoceria resulted in 500 -1000 ug/g nanoceria in the liver and spleen¹⁰⁸. Thus, non-stabilized nanoceria material is often retained in the reticuloendothelial system to a much greater extent than citrate-stabilized particles, regardless of particle size. Not surprisingly, the plasma half-life of these formulations of nanoceria are also short: ~ 7 minutes for non-stabilized nanoceria and 1 hour for citrate stabilized particles, suggesting that more durable coatings increase circulation times and reduce reticuloendothelial system uptake^{133, 135}. However, many of the stabilizers (i.e. citrate, acetate) that are often added to prevent aggregation and optimize surface charge are readily washed off when the particles are exposed to physiological salt solutions. PEGylation appears to desorb from the particle less quickly, thereby increasing plasma circulation times, reducing scavenging by tissue-resident or circulating monocytes as well as reducing deposition in the liver and spleen⁷². Although the characteristics imparted by PEG are a distinct advantage in improving biocompatibility and increasing target tissue accumulation associated with increased circulation times, these benefits are offset by the possibility of diminished catalytic activity of ceria with high density PEG coating in which the surface chemistry dominates chemical reactivity. In addition, depending on the molecular weight of the PEG used in synthesis, significant increases in particle size can occur. Intravenous delivery of 3 nm, PEGylated nanoparticles significantly reduced infarct size following middle cerebral artery occlusion, and the particles resisted agglomeration in high salt solutions for days, illustrative of a highly durable coating that retained catalytic activity for weeks in solution¹⁰⁰. Curiously, these tissue sparing effects were present only at two similar doses (0.5 and 0.7 mg/kg), but not at higher or lower dosing (range = 0.1-1.5 mg/kg intravenous injections).

A unique stabilizer package was recently developed that includes both citrate and the metal chelator EDTA on a 2.9 nm ceria nanoparticle; these Nanoceria distribute to the brain when injected intravenously into mice⁸². This combination of citric acid and EDTA results in highly monodispersed particles that resist agglomeration in high salt solutions and cannot be pelleted out using ultracentrifugation (100,000 x g, 4 degrees Celsius). A hallmark of the importance of this acid/chelator combination is our finding that removal of the citrate from this stabilizer package by either aggressive washing and centrifugation or synthesizing Ce-EDTA particles without citrate eliminates both the ROS neutralizing activity of the particles and their deposition in the brain (unpublished results). Pharmacokinetic studies of these particles administered intravenously in the rat revealed that the half-life of citrate/EDTA nanoceria was 3.7 hours (**Figure 2A**), considerably longer than ceria stabilized with citrate alone and

far longer than 'bare' particles. Again, this supports the use of a more durable stabilizer that seems to avoid active removal by cells of the immune system. Consistent with this notion of reduced clearance by reticuloendothelial organs, tissue levels of nanoceria in the liver and spleen were extremely low in healthy animals⁸² compared to previous studies using 5 nm, citrate stabilized nanoceria at similar time points¹⁰⁸. Renal clearance of negatively charged particles is thought to occur quickly with particles less than 6 nm in size, but nanomaterials larger than 6 nm are likely to end up in the liver and the spleen¹³⁶. The stabilizer package of citric acid and EDTA appears to be unique. Extensive screening of a variety of other biocompatible acids and metal chelator combinations have yielded lower performing particles (unpublished results) tested in a hippocampal brain slice model of oxidative injury⁷⁶ than the combination of citrate and EDTA. Although the chemistry associated with this combination of stabilizers is not yet clear, it is possible that the citric acid may serve as an electron transfer agent between the particle surface and the reactive oxygen species, whereas the EDTA may serve to hold the ceria/citrate complex together. Given that the zeta potential of the citrate/EDTA particle (-23.5 mV) exceeds that of citrate (-20.8 mV) or EDTA alone (-15.7 mV), there may be a synergy with the combination of compounds. Clearly, parsing apart the chemistry will be necessary to understand the chemical interactions of this complex to optimize its biological action.

Clearance of Nanoceria. The clearance of nanoparticles also reflects how the body views the material as a biological entity. High levels of 'bare' or 'citrate stabilized nanoparticles are retained in the liver in rodents up to 90 days post-administration, and, importantly, little decrement was observed in tissue levels over time¹³³. The high concentration and long duration of residence may likely contribute to the observed toxicity in the liver and the spleen associated with these formulations of ceria^{133, 137}. In contrast to these findings, a single 20 mg/kg intravenous dose of citrate/EDTA stabilized nanoceria showed progressive clearance from the brain, liver and spleen over a six month period with large decreases being observed after 3 months in the tissues examined (**Figure 2b-e**) and⁸². The mechanism(s) of ceria clearance in intact animals have not been well studied and are not currently known. Although decreases in ceria content were noted, low levels of ceria in the liver, spleen and brain persist for months⁸², though by 12 months post-injection, ceria levels are near detection limits for most organs (unpublished data). Histopathology of livers harvested from mice administered 30 mg/kg of citrate-EDTA stabilized nanoceria per week for 5 weeks were unremarkable compared to saline injected controls⁸², however the biological effects of lengthy residence times is not currently known. Although quantitative estimates of cerium elimination are rare, it appears that the primary route of elimination for cerium, regardless of route of administration, is through the feces, with smaller (<10%) amounts eliminated in the urine^{138, 139}. It has been suggested that the fecal excretion of systemically absorbed cerium is due to elimination in the bile

¹³⁸, since hepatic clearance was due primarily to biliary function.

Moving forward, additional studies will be needed to identify the clearance routes and evaluate the biological consequences of persistent low levels of ceria in tissues for extended periods of time. Taken together, these data show that the choice of stabilizers and their durability are critical in evaluating the biological impact of metal oxides like nanoceria and their potential for drug development.

Nanoceria's impact on immune system homeostasis. As with any other foreign molecule, the introduction of nanoceria to an organism has the potential to modulate the function of the intact immune system. Typically, the size of individual ceria nanoparticles would allow them to escape detection by the immune system, but any tendency of nanoceria to accumulate into larger aggregates increases the likelihood of uptake by phagocytic immune cells and the potential to initiate an immune response ¹⁴⁰. Further, while nanoceria itself may not be immunogenic, the particles could act as haptens by adsorbing to endogenous proteins of the necessary size and complexity to function as carriers ¹⁴¹. The resultant response is similar to the development of an allergy to drugs like penicillin that become immunogenic in some patients when interacting with host proteins. Thus, selecting the appropriate stabilizer for nanoceria synthesis is also important for minimization of self-aggregation and protein adsorption in the context of the immune system.

Cells of the innate immune system, particularly phagocytic macrophage and neutrophil cells, are those most likely to trigger immediate inflammatory responses to nanoceria exposure. In the skin, resident Langerhans cells (a type of dendritic cell) and rapidly recruited neutrophils and macrophages can clear the area of nanomaterials, but may be triggered by nanoceria aggregates or nanoceria complexing to other proteins to release pro-inflammatory cytokines. Human primary neutrophils exposed to sodium polyacrylate stabilized nanoceria generated increased levels of matrix-metalloproteinase 9 and myeloperoxidase and upregulated markers of degranulation ¹⁴². While these characteristics would be desirable during a response to pathogen exposure, unnecessary release of such tissue destructive enzymes could be damaging to healthy tissues. However, the authors noted aggregation of these nanoparticles ¹⁴², which increases the likelihood that scavenger receptors and complement receptors might be engaged to initiate this behavior. Stabilizing the nanoceria with a coating less likely to trigger aggregation may in fact alleviate this effect. Indeed, the choice of stabilizer and the resulting chemical characteristics did impact uptake by non-immune cell lines in several studies ^{121, 143}. Increased cellular uptake of heparin-functionalized nanoceria compared to non-stabilized nanoceria by a human monocyte cell line is some evidence that stabilizer choice does in fact affect immune cell responses ¹⁴⁴. However, regardless of stabilizer coating, the

nanoceria was able to reduce ROS levels in this activated monocyte cell line ^{144, 145}. Decreased ROS production was also observed in two murine macrophage cell lines that were either unstimulated ¹⁴⁶ or stimulated ¹¹⁷. Uptake of nanoceria and ROS level reduction was observed in a size-dependent manner in activated monocytes ¹⁴⁵, further suggesting that larger individual nanoceria particles (and theoretically nanoceria aggregates) have the potential to be more immunomodulatory than smaller nanoceria that can evade aggregation with itself or other proteins. A consequence of such reduced ROS levels could be impaired innate immune cell destruction of pathogens. Patients with chronic granulomatous disease (CGD) whose macrophages and neutrophils lack the ROS-producing enzyme nicotinamide adenine dinucleotide phosphate (NADPH) oxidase suffer from chronic fungal and bacterial infections due to an inability of these cells to generate sufficient ROS to kill pathogens ¹⁴⁷. Though it is unclear whether nanoceria could reduce ROS to the same levels as in the cells of CGD patients, any degree of ROS reduction may interfere with the ability of innate cells to clear pathogens, thus rendering patients vulnerable to infection.

Though such *in vitro* observations provide some insight into the potential response of immune cells to nanoceria exposure, studies published thus far provide an incomplete picture of how the immune *system* could be affected by such exposure. First, many studies (with the exception of ^{142, 148}) utilize cell lines which, even when they are human lines as opposed to murine cell lines, cannot serve as a perfect proxy for primary human cells. Second, though not a major source of ROS and hence not as involved in oxidative stress, dendritic cells (DCs) must be considered, given their predominant role as the link between the innate and adaptive immune systems. Any immunomodulatory effects on DCs can directly impact the incidence of T cell activation which, if improperly timed, could promote autoimmunity. Third, while *in vitro* cultures allow for focus on specific cell types and specific cell functions, immune cells do not function in isolation in the body. For example, would nanoceria-induced decreases in ROS production in neutrophils and macrophages shift the burden of pathogen clearance and destruction to the complement system or to slower-acting adaptive immune system? Since immune cells function as a *system*, it is quite difficult to fully grasp the extent of nanoceria's effects without studying a whole organism.

Application of nanoceria to oxidative stress-mediated disease. Autoimmune diseases that involve oxidative stress provide a unique opportunity to examine the simultaneous effects of nanoceria on inappropriately activated immune cells and on levels of ROS that also contribute to disease pathology. The autoimmune disease multiple sclerosis (MS) is complex in that it is characterized by different disease progression patterns in part due to the involvement of distinct immune cell populations or combinations of cell populations and their respective cellular secretions ¹⁴⁹. Disease pathogenesis results in the loss of the myelin sheath coating neurons in the central nervous system;

neurons lacking this insulating structure cannot efficiently convey nerve impulses that allow communication between neurons and control of muscles¹⁵⁰. As a result, MS patients suffer loss of motor function and paralysis¹⁵⁰.

Rodent models called experimental autoimmune encephalomyelitis (EAE) replicate the symptoms of MS and are used to investigate both disease pathogenesis as well as potential therapeutic reagents¹⁵¹. The murine model of chronic progressive MS is induced in C57BL/6 mice by targeting immune cell activation against the myelin oligodendrocyte glycoprotein (MOG), eliciting both helper T (TH) cell responses and the involvement of infiltrating macrophages¹⁵¹. TH cells orchestrate the autoimmune destruction of myelin via cytokine production¹⁵⁰. In particular, TH cell-derived cytokines activate macrophages, initiating and amplifying production of pro-inflammatory cytokines and ROS by the macrophages themselves. These ROS generate oxidative stress in the CNS that damages myelin and other macromolecules¹⁵⁰. Application of nanoceria to this disease model would thus enable analysis of two questions about nanoceria. First, can nanoceria retain its functional activity in the intact animal (despite needing to cross numerous biological membrane barriers and forming a protein corona) upon reaching the brain and encountering ROS? Second, how does nanoceria affect immune cells *in vivo* as part on an intact system? If nanoceria was viewed by the body as “foreign” and activated the immune system, one would expect nanoceria to amplify the deleterious effects of immune cells and potentially exacerbate disease symptoms.

When treated with intravenous doses of sodium-citrate stabilized nanoceria, MOG EAE mice displayed fewer motor deficits and less severe clinical symptoms than control animals⁸². The dose of nanoceria delivered correlated with the reduction in disease severity observed as well as with the amount of material detected in the brains of these animals. Brain sections harvested from nanoceria-treated EAE animals late in the disease course also exhibited lower levels of ROS than those harvested from control and fingolimod treated EAE animals, indicating that the antioxidant function of the nanoceria was preserved after entering the CNS compartment (**Figure 3**). The alleviation of disease symptoms suggests that nanoceria at least did not worsen the pro-inflammatory function of TH and macrophage cells, which is also supported by the observation of similar numbers of these cells in the brains of nanoceria vs control animals (**Figure 4**). A more complete analysis of the cytokine secretion and phenotype of these cells is certainly required before a lack of immunomodulatory activity can be concluded. However, several important points can be concluded from this study. First, the stabilized nanoceria was detected in the brain of healthy and EAE animals, in contrast to others who did not detect nanoceria in the brain¹⁰⁷. The sodium citrate stabilization appears to have conferred a favorable distribution pattern to the nanoceria, yielding sufficient levels of particles in the brain to have therapeutic effect while maintaining inherent ROS-neutralizing properties. Second, use of the animal model allowed for

analysis of effects on immune cells altogether in the intact system as opposed to *in vitro* studies of isolated cell types; that the stabilized nanoceria did not appear to aggravate or promote immune cell function is as exciting as the potential therapeutic efficacy observed in this disease model. Thus, when comparing this work to others, it appears that the nuances of particle formulation and stabilization drive the unique distribution, clearance, and functional capacity of nanoceria.

Nanoceria and Eye Diseases – *In Vivo*.

Recent research has focused on the identification and characterization of agents that provide protection to the retina (primarily photoreceptors) against diseases and injury. For the past ten years we have focused primarily on the use of cerium oxide nanoparticles (nanoceria) to prolong vision in animal models of human diseases. The eye is a globe consisting of a tough exterior coat, the sclera, which is continuous with the clear cornea in the front of the eye. The anterior chamber is a fluid filled space beneath the cornea and above the iris (colored part) of the eye. The lens helps to form the bottom part of the anterior chamber and is suspended in the a gel-liquid matrix (vitreous) which fills the interior of the globe and keeps the neural part, the retina, against a thick (Bruch’s) membrane which is in contact with a layer of protective/nourishing cells called Retina Pigment Epithelial (**RPE**) in the back of the eye. The choroid (blood supply) is beneath the RPE and attached to the interior of the sclera. Light passes successively through the cornea, anterior chamber, lens, vitreous and is detected in the back of the eye by the photoreceptors of the retina.

Like the testis and brain, the eye is an immune privileged organ which means that it is not under surveillance by the immune system and the presence of a foreign antigen does not normally produce an inflammatory response. Many neurodegenerative eye diseases have been shown to progress through a common metabolic connection, irrespective of the primary defect causing the disease. This common node is the chronic or acute accumulation of toxic Reactive Oxygen Species (**ROS**) in excess of the cellular defenses. At some undefined threshold of ROS damage, the cell initiates apoptosis or necrosis and dies. It is logical to think that by preventing the ROS damage, one might prevent the death of the cells or at least prolong their lives and function, which in the case of the retina is vision.

Distribution and Retention of nanoceria in the eye. The eye has unique advantages for the study of therapeutic agents because the volume of the eye is small and therefore smaller amounts of a therapeutic agent can be effective. Nanoceria are catalytic antioxidants which mimic the enzymatic activities of superoxide dismutase (SOD) and catalase¹¹⁹. Using inductively coupled plasma mass spectrometry (ICP-MS), we investigated¹⁵² the temporal and spatial distributions of nanoceria in healthy rat retinas after a single intravitreal injection. The data demonstrated (**Figure 5**) that nanoceria were rapidly and preferentially taken up by the retina and, most

surprising to us, the majority of nanoceria were retained in the retina with a half-life of over one year (414 days). No acute or long-term negative effects of nanoceria on retinal function (electroretinography - **ERG**) or cytoarchitecture (histology) were detected at any time point, even after prolonged exposure. These properties indicate that small doses of nanoceria have the potential to provide powerful, long lasting protection against the destructive effects of retinal diseases.

Nanoceria Destroy ROS and Prevent Light-Induced Retinal Degeneration. We initially tested CeNP in primary cell cultures of retinal neurons and found them to be effective in preventing H₂O₂-induced cell death⁵. This led us to test their effectiveness in our “blindness on demand” albino rat model for Age-related Macular Degeneration (**AMD**) in which the extent of retinal degeneration can be controlled by the intensity of light and the duration of exposure. Because the retina is completely contained within the eye, we thought that direct injection of CeNP into the vitreous would enable us to limit the amount of CeNP and provide the highest concentration of CeNP to the retina without requiring that the whole animal be dosed. The retina is about 250 μm thick with the photoreceptor cell layer (125 μm thick) being the furthest distance (~125 μm) from the vitreous. This means that to be effective, the nanoceria must pass through and/or around multiple cell types and must enter photoreceptors to be effective against intracellular ROS which only travel Angstrom distances before reacting with other molecules.

Our experimental paradigm was to inject nanoceria or vehicle into the vitreous of the eye on day 0; three days later expose the rat to bright light for 6 hours; and 7 days later determine retinal function by electroretinography (**ERG**) and end the experiment. Light damage to the retina proceeds through ROS production and our data suggested that Nanoceria decreased light induced ROS in the retina. To evaluate the effectiveness of the CeNP, we examined the histological morphology of the retina and measured its thickness which is directly proportional to the number of rod photoreceptor cells in the retina. Our data indicated that the morphology and rod content of the retina was protected against light damage by CeNP. More significantly, using electroretinography (ERG), the data showed (**Figure 6**) a concentration dependent protection of retinal function with less than $\frac{1}{2}$ nanogram providing significant protection and 3.5 nanograms providing almost complete protection. This study⁵ led us to examine other animal models of human eye diseases.

Inherited Retinal Degeneration. The light damage model exhibits many features of AMD but in keeping with our overarching hypothesis that most eye diseases involve ROS as a major connection between the primary defect and downstream effects, we next examined a mouse model with hereditary eye disease. The *tubby* mouse has inherited retinal degeneration with an early onset and continuous progression to blindness. Our data demonstrated⁸⁹ that systemic delivery of CeNP, via intracardial injections, protect the *tubby* retina by decreasing

ROS, up-regulating the expression of neuroprotection-associated genes; down-regulating apoptosis signaling pathways and/or up-regulating survival signaling pathways to slow photoreceptor degeneration over a two week period. We next tested⁸⁸ the duration of the effects of intravitreal injection of CeNP at Postnatal day (P)7 when examined at P28, P49, P80 and P120. The expression of antioxidant associated genes and photoreceptor-specific genes was significantly up regulated, the mislocalization of rod and cone opsins was decreased, and retinal structure and function were protected.

AMD and Diabetic Retinopathy. Many neurodegenerative diseases are known to occur and progress because of oxidative stress, the presence of ROS in excess of the cellular defensive capabilities. AMD and Diabetic Retinopathy (DR) share oxidative stress as a common node upstream of the blinding effects of these diseases. Knockout of the *very low density lipoprotein receptor (vldlr)* gene results in a mouse that develops pathological intraretinal and subretinal neovascular lesions within the first month of life and is an excellent model for a “wet” form of AMD called retinal angiomas proliferation (**RAP**). We found⁹⁰ that a single intravitreal injection of nanoceria (172 nanograms) into the *vldlr*^{-/-} eye inhibited: the rise in ROS in the retina; increases in vascular endothelial growth factor (VEGF) in the photoreceptor layer; and the formation of intraretinal and subretinal neovascular lesions. Of more therapeutic significance, injection of nanoceria into older mice resulted in the regression of existing vascular lesions indicating that the pathologic neovessels require the continual production of excessive ROS. Our data demonstrate the unique ability of nanoceria to prevent downstream effects of oxidative stress *in vivo* and support their therapeutic potential for treatment of neurodegenerative diseases such as AMD and DR.

Therapeutic Duration of Nanoceria and Pathways Affected. To determine the long-term therapeutic effects and mechanisms of nanoceria action on regression of existing pathologic neovascularization in *vldlr*^{-/-} mouse, young adult mice were injected at P28 and their therapeutic function analyzed through P70¹⁵³. Multiple parameters for nanoceria effects were examined including: regression of existing abnormal blood vessels, reduction of vascular leakage, down-regulation of the expression VEGF, acrolein, glial fibrillary acidic protein (GFAP) and caspase 3 as well as the up-regulation of the expression of rod- and cone-opsin genes and the pro-apoptotic ASK1-P38/JNK/NF κ B signaling pathway. Our data (**Figure 7**) demonstrated that a single intravitreal injection of nanoceria in P28 *vldlr*^{-/-} mice produced sustained regression of existing oxidative stress-induced neovascularizations, prevented blood vessel leakage and inhibited apoptosis via down-regulation of the ASK1-P38/JNK-NF- κ B signaling pathway through P70. The nanoceria do not destroy all ROS and, in the case of the *vldlr*^{-/-} mouse, they do not eliminate all VEGF or have any effect on normal retinal vasculature. This is important because

VEGF is also a neuroprotectant and is necessary for intracellular signaling.

CeNP Effects on Oxidative stress and inflammation. AMD is accompanied by an inflammatory immune response without the presence of any bacterial or viral agent and is referred to as sterile inflammation¹⁵⁴. In our study¹¹⁸, we examined the effect of nanoceria on expression of 88 major cytokines in the retinas of *vldlr*^{-/-} mice using a PCR array. A single intravitreal injection of nanoceria at P28 caused inhibition of pro-inflammatory cytokines and pro-angiogenic growth factors including Tslp, Lif, Il3, Il17, VEGFa, Fgf1, Fgf2, Fgf7, Egf, Efna3, Lep, and up-regulation of several cytokines and anti-angiogenic genes in the *vldlr*^{-/-} retina within one week. An Ingenuity Pathway Analysis software search for biological functions, pathways, and interrelationships between gene networks identified many genes whose activities are involved in cell signaling, cellular development, growth and proliferation, and tissue development. Western blot data analysis revealed that nanoceria inhibit the activation of ERK 1/2, JNK, p38 MAP kinase, and Akt. These data indicate that nanoceria may represent a novel therapeutic strategy to treat AMD, RAP, and other neurodegenerative diseases.

Ocular oncology. Most recently, using a mouse model¹⁵⁵ which develops bilateral retinoblastomas, we demonstrated that a single injection of nanoceria inhibited the growth of the retinoblastoma tumors¹⁵⁶. For this experimental paradigm, after bilateral tumors had developed, the left eye was injected with saline and the right eye with nanoceria in saline and mice were euthanized at one, two and three weeks later. The tumor area was determined on histological serial sections through the entire eye and the total tumor volume in each eye was calculated by summing all of the areas. CeNP injected eyes had 50% less tumor volume over three weeks indicating that CeNP inhibit tumor growth. VEGF in the CeNP injected eyes was also found to be less than half the amount in the saline injected eyes. Histological analysis also showed that most CeNP injected eyes had no metastasis from the posterior chamber of the eye to the anterior chamber whereas all saline or uninjected eyes showed tumor invasion of the anterior chamber. Longitudinal studies on individual mice using small animal Magnetic Resonance Imaging (**MRI**) confirmed the conclusion from the histological data that the volume of the tumors was half as large in the CeNP injected eyes as in the saline injected eyes. However, most intriguing from a therapeutic perspective, the MRI data also demonstrated that the tumors present at the time of CeNP injection decreased by 43% over the three week period and that the blood flow in the tumor of the nanoceria injected eyes was 53% less than that in the saline injected eyes¹⁵⁶ suggesting that one of the mechanisms by which Nanoceria shrink retinoblastomas is by decreasing their access to oxygen and nutrients.

Summary. For all models of eye disease we have studied, the most common feature is the production of excess ROS and this

step appears to be a very early change with multiple downstream signaling pathways being subsequently affected. However, the pattern of change in gene expression appears to be unique for each mutation and/or insult (e.g., light damage) and nanoceria simply reduce the ROS to normal levels in those areas (location, location, location) most affected such as the mitochondria and rod/cone outer segments. When the ROS levels are returned to near normal by nanoceria, there are additional pathways which are affected by these changes. We (unpublished observations) and others have found that simply penetrating the eye with a needle or injecting saline, results in the upregulation of numerous neuroprotective genes and the downregulation of pro-apoptotic genes. However, for rats injected with saline, cDNA microarrays showed that the gene changes induced by saline were transient and returned to normal levels after 24 hours whereas in the eyes of the nanoceria injected rats, these changes continued to be up/down regulated when measured at 48 and 72 hours. These data indicate that the neuroprotective response of the retina to injury is maintained and amplified by nanoceria suggesting that nanoceria would have an additive or synergistic effect when used in a combinatorial manner with other agents which provide a “preconditioning effect”. Such systems are currently being evaluated. Nanoceria are catalytic antioxidants with broad spectrum effects which suggest they may be therapeutic for multiple types of ocular diseases.

Conclusions

It is clear from the depth and scope of the studies reviewed in this critical review that nanoceria is emerging as an anti-inflammatory material. The synthesis and characterization of many different types of nanoceria also show that the chemistry of the surface of these nanoparticles is quite varied, and that interactions with biologically relevant molecules such as proteins, anions and lipids are likely to alter the behaviour of nanoceria *in vivo*. Many questions still remain as to the natural protein corona that builds on nanoceria *in vivo*, and the role it plays in maintaining catalytic activity of nanoceria. Undoubtedly the study of these very intriguing nanoparticles will continue at the interface of biology, biomedical science and material science for years to come.

Acknowledgements

JFM work was supported by NIH NEI grant COBRE-P20 RR017703, P30-EY 12190, R21EY018306, R01EY18724, R01EY022111; National Science Foundation: CBET-0708172; Foundation Fighting Blindness.

This article is a product of a workshop on nanoceria held November 2, 2013 at the Fess Parker Doubletree Resort, Santa Barbara, CA, made possible by financial support from the Sustainable Nanotechnology Organization, The Tracy Farmer Institute for Sustainability and the Environment, the Department of Pharmaceutical Sciences, Associate Dean of

Research of the College of Pharmacy and Office of the Vice President for Research, University of Kentucky.

^a Integrated Nanotechnology and Biomedical Sciences Laboratory, Terrence Donnelly Building, University of Toronto, 160 College St., Toronto, ON M5S 3G9, Canada

^b Advanced Materials Processing and Analysis Centre, Nanoscience Technology Center, University of Central Florida, Orlando, FL, US.

^c Department of Biology, St. Lawrence University, Johnson Hall of Science, 23 Romoda Drive, Canton, NY 13617

^d Department of Biology, Università di Roma Tor Vergata, Via della Ricerca Scientifica, 00133 Roma, Italy^e King Abdullah University of Science and Technology (KAUST), Thuwal 23955-6900, Saudi Arabia

^f Dean A. McGee Eye Institute, Department of Ophthalmology, 608 Stanton L. Young, Blvd., Oklahoma City, OK 73126

^g Burnett School of Biomedical Science, College of Medicine, University of Central Florida, Orlando, Florida 32816

Literature Cited

1. L. M. Cook, *Journal of Non-Crystalline Solids*, 1990, 120, 152-171.
2. K. Reed, A. Cormack, A. Kulkarni, M. Mayton, D. Sayle, F. Klaessig and B. Stadler, *Environmental Science: Nano*, 2014, 1, 390-405.
3. H. Jung, D. B. Kittelson and M. R. Zachariah, *Combustion and Flame*, 2005, 142, 276-288.
4. R. W. Tarnuzzer, J. Colon, S. Patil and S. Seal, *Nano Letters*, 2005, 5, 2573-2577.
5. J. Chen, S. Patil, S. Seal and J. F. McGinnis, *Nature Nanotechnology*, 2006, 1, 142-150.
6. C. A. Cohen, M. D. Kurnick and B. A. Rzigalinski, *Free Radical Biology and Medicine*, 2006, 41, S20-S20.
7. B. A. Rzigalinski, K. Meehan, R. M. Davis, Y. Xu, W. C. Miles and C. A. Cohen, *Nanomedicine (Lond)*, 2006, 1, 399-412.
8. D. Schubert, R. Dargusch, J. Raitano and S. W. Chan, *Biochem Biophys Res Commun*, 2006, 342, 86-91.
9. M. Das, S. Patil, N. Bhargava, J.-F. Kang, L. M. Riedel, S. Seal and J. J. Hickman, *Biomaterials*, 2007, 28, 1918-1925.
10. R. A. Yokel, S. Hussain, S. Garantziotis, P. Demokritou, V. Castranova and F. R. Cassee, *Environmental Science: Nano*, 2014, 1, 406-428.
11. K. Reed, A. Cormack, A. Kulkarni, M. Mayton, D. Sayle, F. Klaessig and B. Stadler, *Environmental Science: Nano*, 2014, 1, 390-405.
12. E. Grulke, K. Reed, M. Beck, X. Huang, A. Cormack and S. Seal, *Environmental Science: Nano*, 2014, 1, 429-444.
13. T. Cedervall, I. Lynch, S. Lindman, T. Berggård, E. Thulin, H. Nilsson, K. A. Dawson and S. Linse, *Proceedings of the National Academy of Sciences*, 2007, 104, 2050-2055.
14. M. P. Monopoli, C. Aberg, A. Salvati and K. A. Dawson, *Nat Nano*, 2012, 7, 779-786.
15. C. D. Walkey and W. C. Chan, *Chem Soc Rev*, 2012, 41, 2780-2799.
16. D. Walczyk, F. B. Bombelli, M. P. Monopoli, I. Lynch and K. A. Dawson, *Journal of the American Chemical Society*, 2010, 132, 5761-5768.
17. P. P. Karmali and D. Simberg, *Expert Opin Drug Deliv*, 2011, 8, 343-357.
18. N. L. Anderson and N. G. Anderson, *Mol Cell Proteomics*, 2002, 1, 845-867.
19. A. L. Barrán-Berdón, D. Pozzi, G. Caracciolo, A. L. Capriotti, G. Caruso, C. Cavaliere, A. Riccioli, S. Palchetti and A. Laganà, *Langmuir*, 2013, 29, 6485-6494.
20. D. Dell'Orco, M. Lundqvist, C. Oslakovic, T. Cedervall and S. Linse, *PLoS One*, 2010, 5, e10949.
21. S. Tenzer, D. Docter, J. Kuharev, A. Musyanovych, V. Fetz, R. Hecht, F. Schlenk, D. Fischer, K. Kiouptsi, C. Reinhardt, K. Landfester, H. Schild, M. Maskos, S. K. Knauer and R. H. Stauber, *Nat Nano*, 2013, 8, 772-781.
22. H. Zhang, K. E. Burnum, M. L. Luna, B. O. Petritis, J. S. Kim, W. J. Qian, R. J. Moore, A. Heredia-Langner, B. J. Webb-Robertson, B. D. Thrall, D. G. Camp, 2nd, R. D. Smith, J. G. Pounds and T. Liu, *Proteomics*, 2011, 11, 4569-4577.
23. T. Cedervall, I. Lynch, M. Foy, T. Berggård, S. C. Donnelly, G. Cagney, S. Linse and K. A. Dawson, *Angew Chem Int Ed Engl*, 2007, 46, 5754-5756.
24. M. P. Monopoli, D. Walczyk, A. Campbell, G. Elia, I. Lynch, F. Baldelli Bombelli and K. A. Dawson, *Journal of the American Chemical Society*, 2011, 133, 2525-2534.
25. C. Rocker, M. Potzl, F. Zhang, W. J. Parak and G. U. Nienhaus, *Nat Nano*, 2009, 4, 577-580.
26. E. Casals, T. Pfäller, A. Duschl, G. J. Oostingh and V. Puntès, *ACS Nano*, 2010, 4, 3623-3632.
27. E. Casals, T. Pfäller, A. Duschl, G. J. Oostingh and V. F. Puntès, *Small*, 2011, 7, 3479-3486.
28. S. Tenzer, D. Docter, S. Rosfa, A. Wlodarski, J. Kuharev, A. Rekić, S. K. Knauer, C. Bantz, T. Nawroth, C. Bier, J. Sirirattanapan, W. Mann, L. Treuel, R. Zellner, M. Maskos, H. Schild and R. H. Stauber, *ACS Nano*, 2011, 5, 7155-7167.
29. C. D. Walkey, J. B. Olsen, H. Guo, A. Emili and W. C. Chan, *J Am Chem Soc*, 2012, 134, 2139-2147.
30. J. H. Shannahan, J. M. Brown, R. Chen, P. C. Ke, X. Lai, S. Mitra and F. A. Witzmann, *Small*, 2013, 9, 2171-2181.
31. Z. J. Deng, G. Mortimer, T. Schiller, A. Musumeci, D. Martin and R. F. Minchin, *Nanotechnology*, 2009, 20, 455101.
32. G. Caracciolo, D. Pozzi, A. Capriotti, C. Cavaliere and A. Laganà, *Journal of Nanoparticle Research*, 2013, 15, 1-11.
33. M. A. Dobrovolskaia, A. K. Patri, J. Zheng, J. D. Clogston, N. Ayub, P. Aggarwal, B. W. Neun, J. B. Hall and S. E. McNeil, *Nanomedicine*, 2009, 5, 106-117.
34. R. E. Serda, J. Gu, R. C. Bhavane, X. Liu, C. Chiappini, P. Decuzzi and M. Ferrari, *Biomaterials*, 2009, 30, 2440-2448.
35. C. C. Fleischer and C. K. Payne, *The Journal of Physical Chemistry B*, 2012, 116, 8901-8907.
36. A. Bajaj, B. Samanta, H. Yan, D. J. Jerry and V. M. Rotello, *Journal of Materials Chemistry*, 2009, 19, 6328-6331.
37. I. Stayton, J. Winiarz, K. Shannon and Y. Ma, *Anal Bioanal Chem*, 2009, 394, 1595-1608.
38. D. Zhang, O. Neumann, H. Wang, V. M. Yuwono, A. Barhoumi, M. Perham, J. D. Hartgerink, P. Wittung-Stafshede and N. J. Halas, *Nano Letters*, 2009, 9, 666-671.

39. R. Tedja, M. Lim, R. Amal and C. Marquis, *ACS Nano*, 2012, 6, 4083-4093.
40. J. T. Quik, I. Lynch, K. Van Hoecke, C. J. Miermans, K. A. De Schampelaere, C. R. Janssen, K. A. Dawson, M. A. Stuart and D. Van De Meent, *Chemosphere*, 2010, 81, 711-715.
41. Y. Zhu, W. Li, Q. Li, Y. Li, Y. Li, X. Zhang and Q. Huang, *Carbon*, 2009, 47, 1351-1358.
42. J. Shi, H. L. Karlsson, K. Johansson, V. Gogvadze, L. Xiao, J. Li, T. Burks, A. Garcia-Bennett, A. Uheida, M. Muhammed, S. Mathur, R. Morgenstern, V. E. Kagan and B. Fadeel, *ACS Nano*, 2012, 6, 1925-1938.
43. D. Guarnieri, A. Guaccio, S. Fusco and P. Netti, *Journal of Nanoparticle Research*, 2011, 13, 4295-4309.
44. C. C. Fleischer, U. Kumar and C. K. Payne, *Biomater Sci*, 2013, 1, 975-982.
45. W. Hu, C. Peng, M. Lv, X. Li, Y. Zhang, N. Chen, C. Fan and Q. Huang, *ACS Nano*, 2011, 5, 3693-3700.
46. A. Lesniak, A. Salvati, M. J. Santos-Martinez, M. W. Radomski, K. A. Dawson and C. Åberg, *Journal of the American Chemical Society*, 2013, 135, 1438-1444.
47. A. Lesniak, F. Fenaroli, M. P. Monopoli, C. Aberg, K. A. Dawson and A. Salvati, *ACS Nano*, 2012, 6, 5845-5857.
48. C. Ge, J. Du, L. Zhao, L. Wang, Y. Liu, D. Li, Y. Yang, R. Zhou, Y. Zhao, Z. Chai and C. Chen, *Proc Natl Acad Sci U S A*, 2011, 108, 16968-16973.
49. C. Li, S. Bolisetty, K. Chaitanya, J. Adamcik and R. Mezzenga, *Adv Mater*, 2013, 25, 1010-1015.
50. K. Furumoto, K. Ogawara, S. Nagayama, Y. Takakura, M. Hashida, K. Higaki and T. Kimura, *J Control Release*, 2002, 83, 89-96.
51. H. Harashima, K. Sakata, K. Funato and H. Kiwada, *Pharm Res*, 1994, 11, 402-406.
52. M. J. Hsu and R. L. Juliano, *Biochim Biophys Acta*, 1982, 720, 411-419.
53. O. Lunov, T. Syrovets, C. Loos, J. Beil, M. Delacher, K. Tron, G. U. Nienhaus, A. Musyanovych, V. Mailander, K. Landfester and T. Simmet, *ACS Nano*, 2011, 5, 1657-1669.
54. S. M. Moghimi, A. C. Hunter and J. C. Murray, *Pharmacol Rev*, 2001, 53, 283-318.
55. X. R. Xia, N. A. Monteiro-Riviere and J. E. Riviere, *Nat Nanotechnol*, 2010, 5, 671-675.
56. A. Gessner, A. Lieske, B. R. Paulke and R. H. Muller, *J Biomed Mater Res A*, 2003, 65, 319-326.
57. H. S. Choi, W. Liu, P. Misra, E. Tanaka, J. P. Zimmer, B. Itty Ipe, M. G. Bawendi and J. V. Frangioni, *Nat Biotechnol*, 2007, 25, 1165-1170.
58. M. Lundqvist, J. Stigler, G. Elia, I. Lynch, T. Cedervall and K. A. Dawson, *Proc Natl Acad Sci U S A*, 2008, 105, 14265-14270.
59. D. E. Owens, 3rd and N. A. Peppas, *Int J Pharm*, 2006, 307, 93-102.
60. J. Satulovsky, M. A. Carignano and I. Szleifer, *Proc Natl Acad Sci U S A*, 2000, 97, 9037-9041.
61. C. H. Choi, C. A. Alabi, P. Webster and M. E. Davis, *Proc Natl Acad Sci U S A*, 2010, 107, 1235-1240.
62. R. Gref, M. Luck, P. Quellec, M. Marchand, E. Dellacherie, S. Harnisch, T. Blunk and R. H. Muller, *Colloids Surf B Biointerfaces*, 2000, 18, 301-313.
63. J. Kreuter, *Adv Drug Deliv Rev*, 2001, 47, 65-81.
64. H. R. Kim, K. Andrieux, S. Gil, M. Taverna, H. Chacun, D. Desmaele, F. Taran, D. Georgin and P. Couvreur, *Biomacromolecules*, 2007, 8, 793-799.
65. J. Kreuter, D. Shamenkov, V. Petrov, P. Ramge, K. Cychutek, C. Koch-Brandt and R. Alyautdin, *J Drug Target*, 2002, 10, 317-325.
66. C. D. Walkey, J. B. Olsen, F. Song, R. Liu, H. Guo, D. W. H. Olsen, Y. Cohen, A. Emili and W. C. W. Chan, *ACS Nano*, 2014, 8, 2439-2455.
67. I. Fridovich, *J Biol Chem*, 1997, 272, 18515-18517.
68. B. Kalyanaraman, *Redox Biol*, 2013, 1, 244-257.
69. A. Karakoti, S. Singh, J. M. Dowding, S. Seal and W. T. Self, *Chem Soc Rev*, 2010, 39, 4422-4432.
70. C. Korsvik, S. Patil, S. Seal and W. T. Self, *Chem Commun (Camb)*, 2007, DOI: 10.1039/b615134e, 1056-1058.
71. E. G. Heckert, A. S. Karakoti, S. Seal and W. T. Self, *Biomaterials*, 2008, 29, 2705-2709.
72. A. S. Karakoti, S. Singh, A. Kumar, M. Malinska, S. V. Kuchibhatla, K. Wozniak, W. T. Self and S. Seal, *J Am Chem Soc*, 2009, 131, 14144-14145.
73. V. Singh, S. Singh, S. Das, A. Kumar, W. T. Self and S. Seal, *Nanoscale*, 2012, 4, 2597-2605.
74. S. Singh, T. Dosani, A. S. Karakoti, A. Kumar, S. Seal and W. T. Self, *Biomaterials*, 2011, 32, 6745-6753.
75. T. Naganuma and E. Traversa, *Biomaterials*, 2014, 35, 4441-4453.
76. A. Y. Estevez, S. Pritchard, K. Harper, J. W. Aston, A. Lynch, J. J. Lucky, J. S. Ludington, P. Chatani, W. P. Mosenthal, J. C. Leiter, S. Andreescu and J. S. Erlichman, *Free Radic Biol Med*, 2011, 51, 1155-1163.
77. M. Ganesana, J. S. Erlichman and S. Andreescu, *Free Radic Biol Med*, 2012, 53, 2240-2249.
78. T. X. Sayle, M. Molinari, S. Das, U. M. Bhatta, G. Mobus, S. C. Parker, S. Seal and D. C. Sayle, *Nanoscale*, 2013, 5, 6063-6073.
79. T. Pirmohamed, J. M. Dowding, S. Singh, B. Wasserman, E. Heckert, A. S. Karakoti, J. E. King, S. Seal and W. T. Self, *Chem Commun (Camb)*, 2010, 46, 2736-2738.
80. S. I. Liochev, *Free Radical Biology and Medicine*, 2013, 60, 1-4.
81. S. S. Lee, W. Song, M. Cho, H. L. Puppala, P. Nguyen, H. Zhu, L. Segatori and V. L. Colvin, *ACS Nano*, 2013, DOI: 10.1021/nn4026806.
82. K. L. Heckman, W. DeCoteau, A. Estevez, K. J. Reed, W. Costanzo, D. Sanford, J. C. Leiter, J. Clauss, K. Knapp, C. Gomez, P. Mullen, E. Rathbun, K. Prime, J. Marini, J. Patchefsky, A. S. Patchefsky, R. K. Hailstone and J. S. Erlichman, *ACS Nano*, 2013, 7, 10582-10596.
83. J.-D. Cafun, K. O. Kvashnina, E. Casals, V. F. Puentes and P. Glatzel, *ACS Nano*, 2013, 7, 10726-10732.
84. J. M. Dowding, T. Dosani, A. Kumar, S. Seal and W. T. Self, *Chem Commun (Camb)*, 2012, 48, 4896-4898.
85. P. Pacher, J. S. Beckman and L. Liaudet, *Physiol Rev*, 2007, 87, 315-424.
86. J. M. Dowding, S. Das, A. Kumar, T. Dosani, R. McCormack, A. Gupta, T. X. T. Sayle, D. C. Sayle, L. von Kalm, S. Seal and W. T. Self, *ACS Nano*, 2013, 7, 4855-4868.
87. J. M. Dowding, S. Seal and W. T. Self, *Drug Deliv Transl Res*, 2013, 3, 375-379.
88. X. Cai, S. A. Sezate, S. Seal and J. F. McGinnis, *Biomaterials*, 2012.
89. L. Kong, X. Cai, X. Zhou, L. L. Wong, A. S. Karakoti, S. Seal and J. F. McGinnis, *Neurobiology of disease*, 2011, 42, 514-523.

90. X. Zhou, L. L. Wong, A. S. Karakoti, S. Seal and J. F. McGinnis, *PLoS one*, 2011, 6, e16733.
91. J. Colon, L. Herrera, J. Smith, S. Patil, C. Komanski, P. Kupelian, S. Seal, D. W. Jenkins and C. H. Baker, *Nanomedicine: Nanotechnology, Biology and Medicine*, 2009, 5, 225-231.
92. M. S. Wason, J. Colon, S. Das, S. Seal, J. Turkson, J. Zhao and C. H. Baker, *Nanomedicine: Nanotechnology, Biology and Medicine*, 2012.
93. S. Das, S. Singh, J. M. Dowding, S. Oommen, A. Kumar, T. X. Sayle, S. Saraf, C. R. Patra, N. E. Vlahakis and D. C. Sayle, *Biomaterials*, 2012.
94. S. Chigurupati, M. R. Mughal, E. Okun, S. Das, A. Kumar, M. McCaffery, S. Seal and M. P. Mattson, *Biomaterials*, 2012.
95. A. S. Karakoti, O. Tsigkou, S. Yue, P. D. Lee, M. M. Stevens, J. R. Jones and S. Seal, *Journal of Materials Chemistry*, 2010, 20, 8912-8919.
96. R. Davan, R. Prasad, V. S. Jakka, R. Aparna, A. Phani, B. Jacob, P. C. Salins and D. Raju, *Journal of Bionanoscience*, 2012, 6, 78-83.
97. A. Cimini, B. D'Angelo, S. Das, R. Gentile, E. Benedetti, V. Singh, A. M. Monaco, S. Santucci and S. Seal, *Acta Biomaterialia*, 2012, 8, 2056-2067.
98. B. D'Angelo, S. Santucci, E. Benedetti, S. Di Loreto, R. Phani, S. Falone, F. Amicarelli, M. P. Ceru and A. Cimini, *Current Nanoscience*, 2009, 5, 167-176.
99. W. DeCoteau, A. Estevez, S. Leo-Nyquist, K. Heckman, K. Reed and J. Erlichman, 2011.
100. C. K. Kim, T. Kim, I.-Y. Choi, M. Soh, D. Kim, Y.-J. Kim, H. Jang, H.-S. Yang, J. Y. Kim, H.-K. Park, S. P. Park, S. Park, T. Yu, B.-W. Yoon, S.-H. Lee and T. Hyeon, *Angewandte Chemie*, 2012, 124, 11201-11205.
101. L. Alili, M. Sack, A. S. Karakoti, S. Teuber, K. Puschmann, S. M. Hirst, C. M. Reilly, K. Zanger, W. Stahl, S. Das, S. Seal and P. Brenneisen, *Biomaterials*, 2011, 32, 2918-2929.
102. L. Alili, M. Sack, C. von Montfort, S. Giri, S. Das, K. S. Carroll, K. Zanger, S. Seal and P. Brenneisen, *Antioxidants & redox signaling*, 2012.
103. S. Giri, A. Karakoti, R. P. Graham, J. L. Maguire, C. M. Reilly, S. Seal, R. Rattan and V. Shridhar, *PLoS one*, 2013, 8, e54578.
104. K. Chaudhury, N. K. Babu, S. Das, A. Kumar and S. Seal, *Nanomedicine: Nanotechnology, Biology and Medicine*, 2012.
105. S. Patil, A. Sandberg, E. Heckert, W. Self and S. Seal, *Biomaterials*, 2007, 28, 4600-4607.
106. S. Singh, A. Kumar, A. Karakoti, S. Seal and W. T. Self, *Molecular BioSystems*, 2010, 6, 1813-1820.
107. S. M. Hirst, A. Karakoti, S. Singh, W. Self, R. Tyler, S. Seal and C. M. Reilly, *Environmental Toxicology*, 2013, 28, 107-118.
108. R. A. Yokel, M. T. Tseng, M. Dan, J. M. Unrine, U. M. Graham, P. Wu and E. A. Grulke, *Nanomedicine: Nanotechnology, Biology and Medicine*, 2012.
109. I. Celardo, J. Z. Pedersen, E. Traversa and L. Ghibelli, *Nanoscale*, 2011, 3, 1411-1420.
110. I. Celardo, M. De Nicola, C. Mandoli, J. Z. Pedersen, E. Traversa and L. Ghibelli, *ACS Nano*, 2011, 5, 4537-4549.
111. M. De Nicola, G. Gualandi, A. Alfonsi, C. Cerella, M. D'Alessio, A. Bergamaschi, A. Magrini and L. Ghibelli, *Biochem Pharmacol*, 2006, 72, 1405-1416.
112. L. Ghibelli, C. Fanelli, G. Rotilio, E. Lafavia, S. Coppola, C. Colussi, P. Civitareale and M. R. Ciriolo, *FASEB J*, 1998, 12, 479-486.
113. M. T. Kuo, *Antioxid Redox Signal*, 2009, 11, 99-133.
114. D. Gonzalez-Flores, M. De Nicola, E. Bruni, F. Caputo, A. B. Rodriguez, J. A. Pariente and L. Ghibelli, *Mol Cell Biochem*, 2014, DOI: 10.1007/s11010-014-2192-2.
115. J. Colon, N. Hsieh, A. Ferguson, P. Kupelian, S. Seal, D. W. Jenkins and C. H. Baker, *Nanomedicine*, 2010, 6, 698-705.
116. J. Niu, K. Wang and P. E. Kolattukudy, *J Pharmacol Exp Ther*, 2011, 338, 53-61.
117. S. M. Hirst, A. S. Karakoti, R. D. Tyler, N. Sriranganathan, S. Seal and C. M. Reilly, *Small*, 2009, 5, 2848-2856.
118. S. V. Kyosseva, L. Chen, S. Seal and J. F. McGinnis, *Exp Eye Res*, 2013, 116, 63-74.
119. S. Das, J. M. Dowding, K. E. Klump, J. F. McGinnis, W. Self and S. Seal, *Nanomedicine (Lond)*, 2013, 8, 1483-1508.
120. J. M. Perez, A. Asati, S. Nath and C. Kaittanis, *Small*, 2008, 4, 552-556.
121. M. Safi, H. Sarrouj, O. Sandre, N. Mignet and J. F. Berret, *Nanotechnology*, 2010, 21, 145103.
122. F. Caputo, M. De Nicola and L. Ghibelli, *Biochem Pharmacol*, 2014, DOI: 10.1016/j.bcp.2014.08.015.
123. A. Briggs, S. Corde, S. Oktaria, R. Brown, A. Rosenfeld, M. Lerch, K. Konstantinov and M. Tehei, *Nanomedicine*, 2013, 9, 1098-1105.
124. G. F. Tomaselli and A. S. Barth, *Nat Med*, 2010, 16, 648-649.
125. G. Forte, F. Carotenuto, F. Pagliari, S. Pagliari, P. Cossa, R. Fiaccavento, A. Ahluwalia, G. Vozzi, B. Vinci, A. Serafino, A. Rinaldi, E. Traversa, L. Carosella, M. Minieri and P. Di Nardo, *Stem Cells*, 2008, 26, 2093-2103.
126. L. Shao, H. Li, S. K. Pazhanisamy, A. Meng, Y. Wang and D. Zhou, *Int J Hematol*, 2011, 94, 24-32.
127. A. Mohyeldin, T. Garzon-Muvdi and A. Quinones-Hinojosa, *Cell Stem Cell*, 2010, 7, 150-161.
128. C. Mandoli, F. Pagliari, S. Pagliari, G. Forte, P. Di Nardo, S. Licoccia and E. Traversa, *Advanced Functional Materials*, 2010, 20, 1617-1624.
129. W. F. B. Boron, Emile L., *Medical Physiology: a cellular and molecular approach*, Saunders/Elsevier, 2009.
130. J. Niu, A. Azfer, L. M. Rogers, X. Wang and P. E. Kolattukudy, *Cardiovasc Res*, 2007, 73, 549-559.
131. S. S. Hardas, D. A. Butterfield, R. Sultana, M. T. Tseng, M. Dan, R. L. Florence, J. M. Unrine, U. M. Graham, P. Wu, E. A. Grulke and R. A. Yokel, *Toxicol Sci*, 2010, 116, 562-576.
132. P. L. Rodriguez, T. Harada, D. A. Christian, D. A. Pantano, R. K. Tsai and D. E. Discher, *Science*, 2013, 339, 971-975.
133. R. A. Yokel, T. C. Au, R. MacPhail, S. S. Hardas, D. A. Butterfield, R. Sultana, M. Goodman, M. T. Tseng, M. Dan, H. Haghazari, J. M. Unrine, U. M. Graham, P. Wu and E. A. Grulke, *Toxicol Sci*, 2012, 127, 256-268.
134. S. S. Hardas, R. Sultana, G. Warrier, M. Dan, R. L. Florence, P. Wu, E. A. Grulke, M. T. Tseng, J. M. Unrine, U. M. Graham, R. A. Yokel and D. A. Butterfield, *Neurotoxicology*, 2012, 33, 1147-1155.
135. M. Dan, M. T. Tseng, P. Wu, J. M. Unrine, E. A. Grulke and R. A. Yokel, *Int J Nanomedicine*, 2012, 7, 4023-4036.

136. A. Albanese, P. S. Tang and W. C. Chan, *Annu Rev Biomed Eng*, 2012, 14, 1-16.
137. M. T. Tseng, X. Lu, X. Duan, S. S. Hardas, R. Sultana, P. Wu, J. M. Unrine, U. Graham, D. A. Butterfield, E. A. Grulke and R. A. Yokel, *Toxicol Appl Pharmacol*, 2012, 260, 173-182.
138. C. S. B. Lustgarden, B.B., Cuddihy, R. G et al., *Biliary excretion of ¹⁴⁴Ce after inhalation of ¹⁴⁴Ce citrate in rats and Syrian hamsters.*, Lovelace Foundation for Medical Education and Research, 1976.
139. P. W. Durbin, M. H. Williams, M. Gee, R. H. Newman and J. G. Hamilton, *Proc Soc Exp Biol Med*, 1956, 91, 78-85.
140. W. Wang, S. K. Singh, N. Li, M. R. Toler, K. R. King and S. Nema, *Int J Pharm*, 2012, 431, 1-11.
141. J. Uetrecht and D. J. Naisbitt, *Pharmacol Rev*, 2013, 65, 779-808.
142. K. Babin, F. Antoine, D. M. Goncalves and D. Girard, *Toxicol Lett*, 2013, 221, 57-63.
143. A. Asati, S. Santra, C. Kaittanis and J. M. Perez, *ACS Nano*, 2010, 4, 5321-5331.
144. S. R. Ting, J. M. Whitelock, R. Tomic, C. Gunawan, W. Y. Teoh, R. Amal and M. S. Lord, *Biomaterials*, 2013, 34, 4377-4386.
145. M. S. Lord, M. Jung, W. Y. Teoh, C. Gunawan, J. A. Vassie, R. Amal and J. M. Whitelock, *Biomaterials*, 2012, 33, 7915-7924.
146. T. Xia, M. Kovochich, M. Liang, L. Madler, B. Gilbert, H. Shi, J. I. Yeh, J. I. Zink and A. E. Nel, *ACS Nano*, 2008, 2, 2121-2134.
147. D. Roos and M. de Boer, *Clin Exp Immunol*, 2013, DOI: 10.1111/cei.12202.
148. S. Hussain, F. Al-Nsour, A. B. Rice, J. Marshburn, B. Yingling, Z. Ji, J. I. Zink, N. J. Walker and S. Garantziotis, *ACS Nano*, 2012, 6, 5820-5829.
149. A. Nylander and D. A. Hafler, *J Clin Invest*, 2012, 122, 1180-1188.
150. H. Lassmann and J. van Horssen, *FEBS Lett*, 2011, 585, 3715-3723.
151. E. Mix, H. Meyer-Rienecker, H. P. Hartung and U. K. Zettl, *Prog Neurobiol*, 2010, 92, 386-404.
152. L. L. Wong, S. M. Hirst, Q. N. Pye, C. M. Reilly, S. Seal and J. F. McGinnis, *PLoS One*, 2013, 8, e58431.
153. X. Cai, S. Seal and J. F. McGinnis, *Biomaterials*, 2014, 35, 249-258.
154. S. L. Doyle, M. Campbell, E. Ozaki, R. G. Salomon, A. Mori, P. F. Kenna, G. J. Farrar, A. S. Kiang, M. M. Humphries, E. C. Lavelle, L. A. O'Neill, J. G. Hollyfield and P. Humphries, *Nat Med*, 2012, 18, 791-798.
155. J. Zhang, B. Schweers and M. A. Dyer, *Cell Cycle*, 2004, 3, 952-959.
156. K. E. Klump, X. Cai, R. Towner, S. Seal, M. Dyer and J. McGinnis, *The FASEB Journal*, 2013, 27, 1088.1016.

Figure legends

Figure 1. CeO₂ NPs accelerate the decay of peroxynitrite *in vitro*. (A) Relative absorbance of peroxynitrite (25 μM) at 320 nm over time (seconds) either in the absence or presence of CeO₂ nanoparticles (100 μM), SiO₂ nanoparticles (100 μM), uric acid (UA) (1 mM), or glutathione (GSH) (0.5 mM). (B) Relative APF (10 μM) fluorescence at 490 nm excitation and 515 nm emission wavelength of either peroxynitrite (20 μM) alone, or in combination with CeO₂ nanoparticles (100 μM), SiO₂ nanoparticles (100 μM), uric acid (1 mM), or glutathione (0.5 mM) measured over a time period of 14 seconds. Data are representative of three or more experiments. Reproduced with permission from Drug Discovery and Translational Research⁸⁷.

Figure 2. Citrate-EDTA stabilized nanoparticles exhibit a relatively lengthy half-life and can penetrate the blood brain barrier. (A) Sprague Dawley rats were injected intravenously with 10mg/kg Nanoceria, and the blood ceria content was measured by ICP-MS over time. (B-E) Healthy SJL/J mice were injected once intravenously with 20mg/kg Nanoceria, and tissues were harvested at various time points to assess ceria content by ICP-MS. The amount of ceria in each tissue at 24 hours post-injection is indicated as “Load”.

Figure 3. Mice with a model of multiple sclerosis exhibit lower ROS levels in the hippocampus when treated with citrate-EDTA stabilized Nanoceria. Experimental autoimmune encephalomyelitis was induced in female C57BL/6 mice, and animals were treated with intravenous injections of saline control or 30 mg/kg Nanoceria (days -1, 0, 3, 7, 14, 21, 28, 35) or were treated orally with fingolimod beginning on day 7 (2ug/L). Beginning on day 42, animals were perfused with PBS post-euthanization, and harvested brains were sliced and stained with CM-H₂DCFDA fluorophore to detect total ROS (A). (B) Separate sections were stained with an anti-laminin antibody to visualize the vasculature in the brain. (C) ROS levels in brain slices from CeNP treated (left) or control (right) animals. G/P: granular purkinje. M: molecular layer. NS: not significant.


Figure 4. Macrophage and TH cell populations in the brains of mice with a model of multiple sclerosis are not significantly altered by citrate-EDTA stabilized CeNP treatment. Mice with experimental autoimmune encephalomyelitis were treated with intravenous doses of control saline, or 10 mg/kg Nanoceria in a preventative (days -1,0, 3, 7, 14, 21, 28) or therapeutic treatment (days 3, 7, 14, 21, 28) regimen. Brains were harvested from PBS-perfused euthanized animals on day 45 and lymphocyte populations were identified by antibody stains: (A) CD4-PE for TH cells, (B) CD45-PE and CD11b-PerCp for macrophages.


Figure 5. CeNP are retained in the retina with a half-life of 414 days. CeNP (344ng) were injected into the vitreous of the eye,


the retina was dissected and cerium was determined by ICP-MS at the indicated times. [Modified from reference Wong 2013)


Figure 6. CeNP provide concentration dependent protection of retinal function from light damage. Waveform ERG data. See text for details. [modified from ref (4)].


Figure 7. CeNP (172 ng at P28) decrease neovascularization and leakage as visualized by fluorescence funduscopy at P49. The columns are as labeled and the rows are images at (1) 2 min, (2) 4 min and (3) 6 min after fluorescein injection. The normal retinal vasculature is seen in the wild type (wt). The many leaky neovascularizations seen in untreated vldlr^{-/-} mice are remarkably reduced by CeNP. [Modified from Cai-2013)]

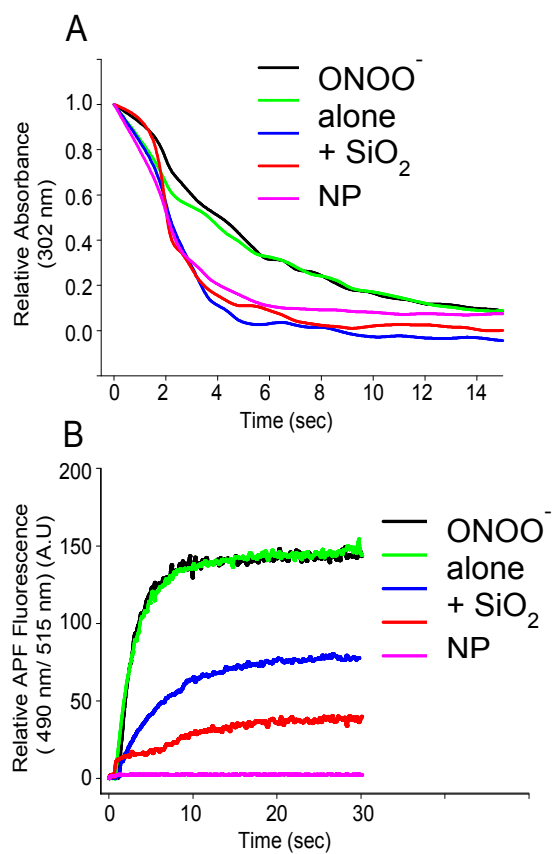


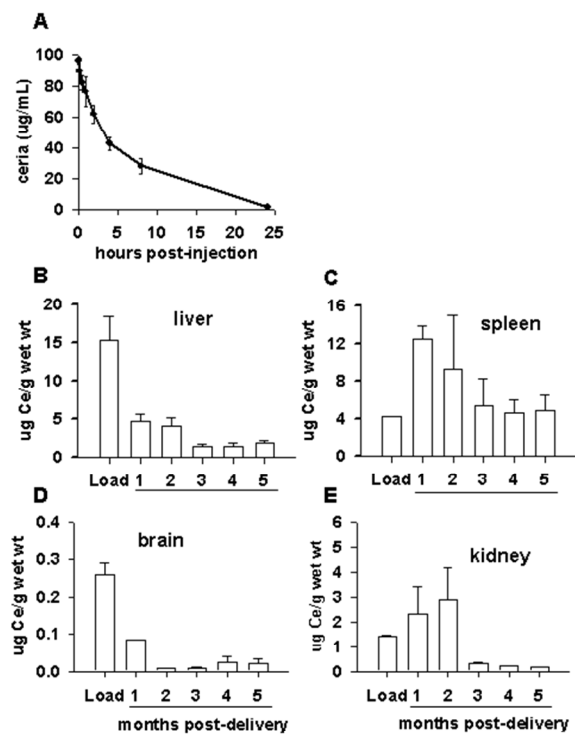


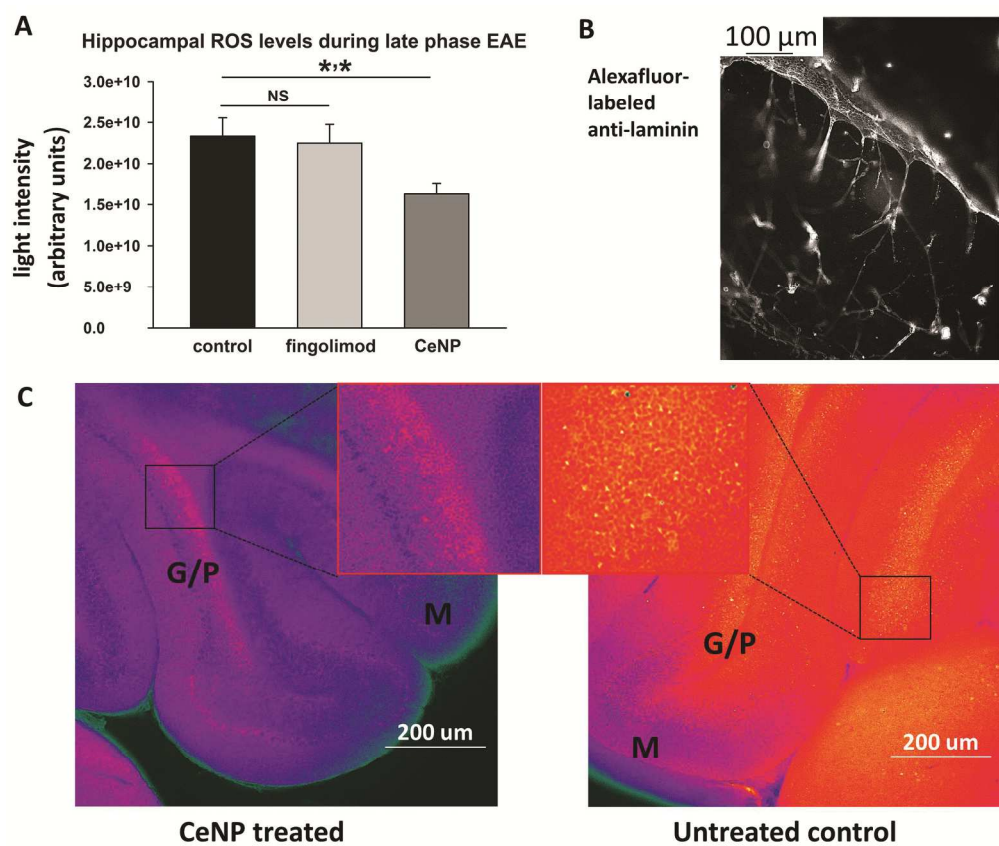

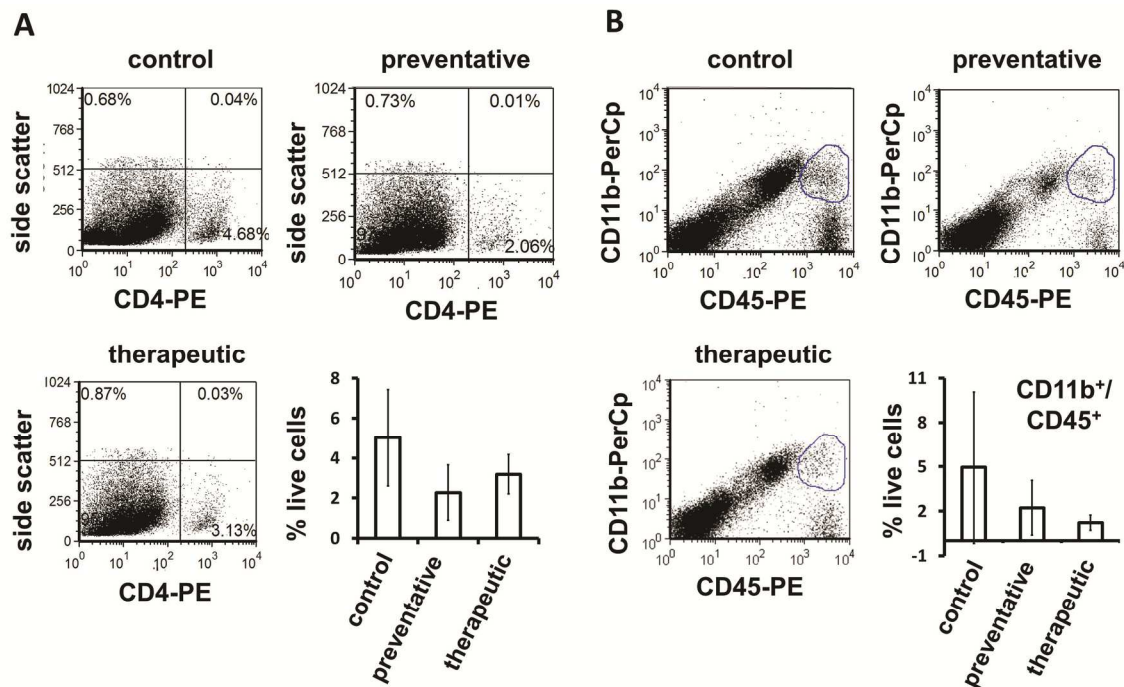

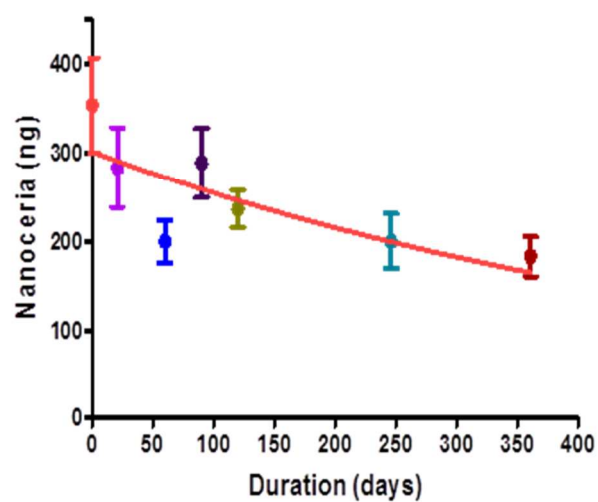

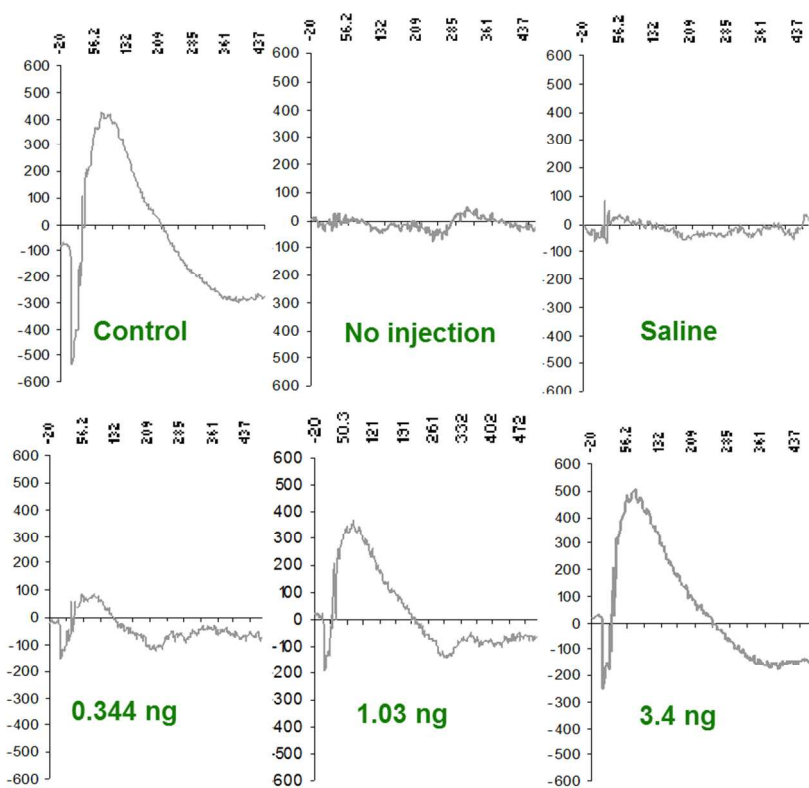

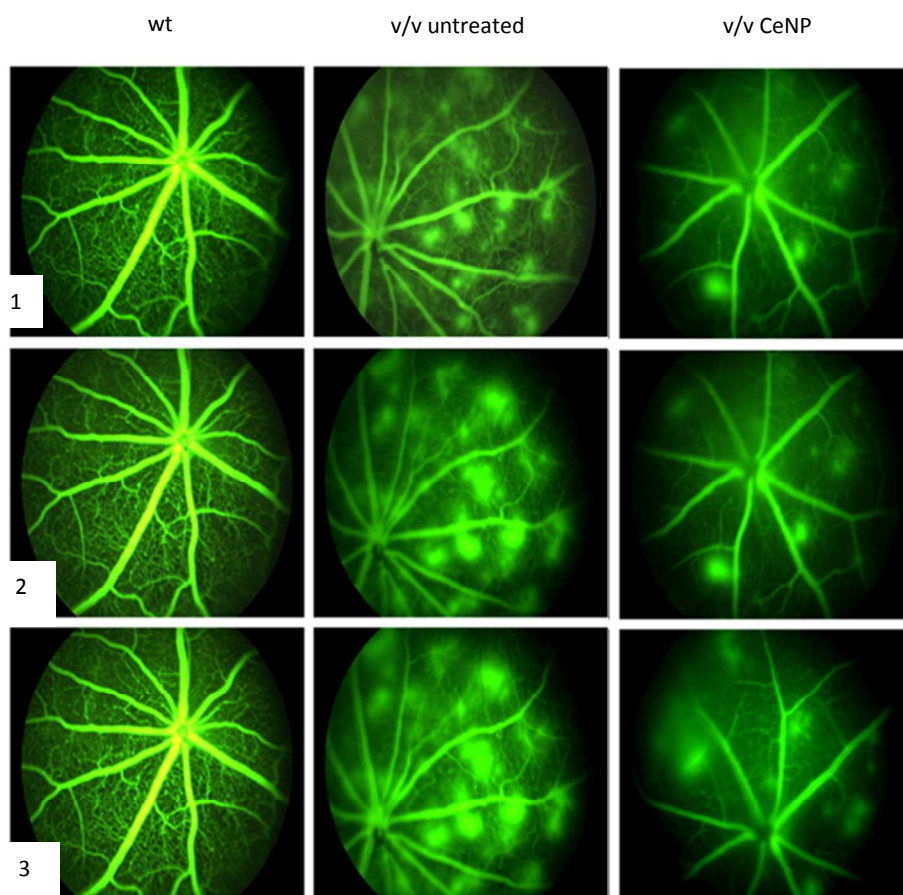



Group photo caption: (From left to right; top row) Carl Walkey, Sudipta Seal, Soumen Das, William T. Self; (bottom row) James F. McGinnis, Karin L. Heckman, Joe Erlichman, Enrico Traversa

Carl Walkey received his B.Eng. from Carleton University in 2007 and his PhD from the University of Toronto in 2014. His doctoral research focused on tailoring the nano-bio interface to optimize the performance of nanomaterials in diagnostic and therapeutic applications and was supervised by Dr. Warren Chan at the Institute of Biomaterials and Biomedical Engineering.

Sudipta Seal is a UCF Distinguished Professor and Pegasis Professor in Materials Science and Engineering, School of medicine and interim chair and director of the Advanced Materials Processing and Analysis Center and the Nanoscience Technology Center, University of Central Florida. He is a Fellow of ASM, AVS, IoN, AAAS, NAI, ECS, AIMBE and a recipient of Office of Naval Research Young Investigator Award (ONR YIP). His current research involves functional nanoparticles for energy, biomedical and sensor applications, and green manufacturing. He has coauthored more than 300 papers, numerous book chapters, three books on nanotechnology, and has been awarded 40 patents.

Soumen Das received his PhD from Indian Institute of Technology, Kharagpur in 2010. Currently he is working as a Research assistant professor in Advanced Materials Processing and Analysis Center and Nanoscience Technology Center, University of Central Florida, Orlando. His research is focused on the synthesis and conjugation of biomolecules to rare earth nanoparticles as targeted therapeutic agents and understanding the interaction mechanism of nanoparticles with cells. He is coauthor of 36 papers and 1 patent has been awarded. He has own GRC speaker award, UCF 2012 innovator award, Dr. D.S. Kothari Postdoctoral fellowship and CSIR fellowship.

William T. Self obtained his Ph.D. in Microbiology from the University of Florida in 1998, working with Dr. K. T. Shanmugam and studying microbial physiology using *Escherchia coli* as a model. He moved to the NIH in Bethesda, Maryland and was a Research Fellow under the tutelage of Dr. Thressa Stadtman studying selenoprotein biochemistry. He moved to UCF in 2003 and is now an Associate Professor in the Burnett School of Biomedical Science. His lab is now more focused on the study of the catalytic behavior of cerium oxide nanomaterials and moving this material into clinical applications in medicine.

James F. McGinnis is a Professor in the departments of Cell Biology and Ophthalmology at Oklahoma University Center for Health Sciences, Director of the Dean McGee Eye Institute Cell Imaging Core, and Associate Director of the Oklahoma Center for Neuroscience. Over the last ten years, his lab has been using nanoceria to protect retinal neurons from Reactive Oxygen Species induced death in multiple animal models for recessive and dominant forms of inherited retinal degeneration (RP), Age-related Macular Degeneration (AMD), Diabetic Retinopathy (DR), Retinoblastoma (Rb) and Retinopathy of Prematurity (ROP). Current efforts are focused on the demonstration of the molecular mechanisms by which nanoceria function in vivo and the advancement of nanoceria as an FDA approved Investigational New Drug (IND) for safe use in humans.

Karin L. Heckman PhD, RD is an Assistant Professor of Biology at St. Lawrence University in Canton, NY. She earned her BS degree in Community/Medical Dietetics at Viterbo University in La Crosse, WI prior to becoming credentialed as a Registered Dietitian. She went on to complete her PhD in Biomedical Science: Immunology at the Mayo Clinic College of Medicine in Rochester, MN.

Joe Erlichman received his Ph.D. from Dartmouth Medical School and additional post-doctoral training at Dartmouth Medical School and Boonshoft School of Medicine in Dayton, Ohio. He is a past recipient of the American Physiological Societies Van Harreveld Memorial Award in central nervous system studies and currently is professor at St. Lawrence University in the Department of Biology/Program in Neuroscience. In addition to his academic appointments, Dr. Erlichman co-founded Neuroredox, LLC and Cerion NRx, LLC and currently serves the Chief Scientific Officer for these organizations. His current research interests involve the development of novel, ceria-based therapeutics in the treatment of neurodegenerative diseases.

Enrico Traversa received his PhD in Chemical Engineering from the University of Rome La Sapienza. In 2013 he joined the King Abdullah University of Science and Technology (KAUST), Saudi Arabia, as Professor of Materials Science and Engineering, after being the Director of the Department of Fuel Cell Research at the International Center for Renewable Energy, Xi'an Jiaotong University, China. He joined the University of Rome Tor Vergata, Italy, in 1988, where he is a Professor of Materials Science and Technology, now on leave of absence. From January 2009 to March 2012, he was a Principal Investigator at the International Research Center for Materials Nanoarchitectonics (MANA) at the National Institute for Materials Science (NIMS), Tsukuba, Japan, leading a unit on Sustainability Materials. His research interests include nanostructured materials for environment, energy, and healthcare, with special attention to sustainable development, and he was elected as a Fellow of the Electrochemical Society in 2013.

Nanoceria - CeO_{2-x}

Redox active nanoparticles
targeting ROS and RNS

