


Nanoscale

Accepted Manuscript

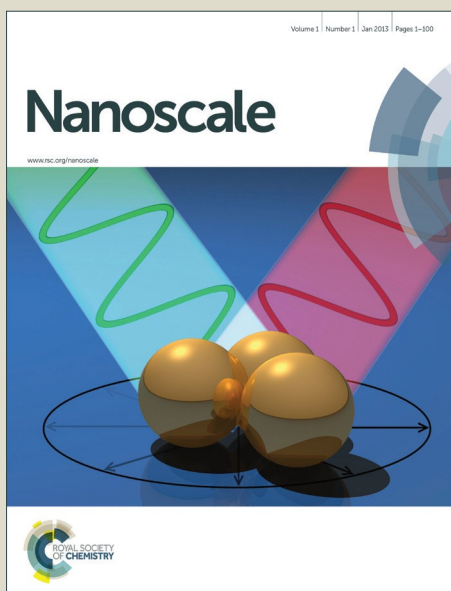

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Porous metallic MoO₂-supported MoS₂ Nanosheets for enhanced electrocatalytic activity in hydrogen evolution reaction[†]

Cite this: DOI: 10.1039/x0xx00000x

Linjing Yang^a, Weijia Zhou^{a*}, Dongman Hou^b, Kai Zhou^a, Guoqiang Li^b, Zhenghua Tang^a, Ligui Li^a, and Shaowei Chen^{a,c*}

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Advanced materials for electrocatalytic water splitting are central to renewable energy research. In this work, MoS₂ nanosheets supported on porous metallic MoO₂ (MoS₂/MoO₂) were produced by sulfuration treatments of porous highly conductive MoO₂ for hydrogen evolution reaction. Porous MoO₂ with one-dimensional channel-like structures was prepared by calcination at elevated temperatures using phosphomolybdic acid as the precursor and mesoporous silica (SBA-15) as the template, and subsequent hydrothermal treatment in the presence of thioacetamide led to the transformation of the top layers to MoS₂ forming MoS₂/MoO₂ composites. Electrochemical studies showed that the obtained composites exhibited excellent electrocatalytic activity for HER with an onset potential of −104 mV (vs RHE), a large current density (10 mA/cm² at −0.24 V), a small Tafel slope of 76.1 mV/dec and robust electrochemical durability. The performance might be ascribed to the high electrical conductivity and porous structures of MoO₂ with one-dimensional channels of 3 to 4 nm in diameter that allowed for fast charge transport and collection.

Introduction

As a clean chemical fuel with a high-energy density, hydrogen has been hailed as a promising alternative and renewable energy source that may replace fossil fuels in the future. Accordingly, hydrogen produced by environmentally friendly electrochemical water splitting has recently been emerging as a key technology component of hydrogen economy.^{1–4} In these studies, advanced catalysts for the hydrogen evolution reaction (HER) are generally needed to reduce overpotential and increase catalytic current density.^{5–11} Pt-group metals are the most active catalysts for HER and can dramatically enhance the reaction rate with almost no overpotential for high efficiency energy conversion.¹² However, their scarcity and high costs have inhibited large scale applications in electrochemical water splitting. Therefore, extensive research efforts have been devoted to the development of non-platinum electrocatalysts for HER. For instance, Hinnemann et al.¹³ reported in 2005 that MoS₂ nanoparticles exhibited apparent electrocatalytic activity for HER, which was predicted to be comparable to that of Pt. The interest in using MoS₂ as water splitting electrocatalysts has since been intensified, with a focus on the enhancement of the material catalytic properties by, for instance, loading catalysts on conductive substrates (e.g., graphene-protected 3D

Ni foams, graphene nanosheets, and porous Au),^{14–17} doping treatment (e.g. MoO₂/N-doped MoS₂ and oxygen incorporated MoS₂),^{18, 19} and enhanced exposure of active edges.^{20–22} Among these, Chang et al.¹⁴ deposited graphene layers on the surface of 3D Ni foams and used them as a conducting solid support for MoS_x. The hydrogen evolution rate was found to reach 302 mL/g cm² h at an overpotential of −200 mV, where the Ni foams-supported graphene sheets served as a robust scaffold and increased the stability of the catalysts in acid. In another study, Ge et al.¹⁵ reported a new type of nanoporous electrocatalysts by chemically plating a thin layer of amorphous molybdenum sulfide on the internal surface of dealloyed nanoporous gold. The resulting MoS_{2.7}@Au electrode exhibits 6-fold higher catalytic activity than conventional molybdenum sulfide catalysts in a 0.5 M H₂SO₄ solution with a Tafel slope of 41 mV/dec. The improved catalytic performance was mainly due to the highly conductive and large-surface nanoporous gold. However, porous Au is expensive. Is it possible to find low-cost porous conductive substrates for the synthesis of high-performance HER catalysts? This is the primary motivation of the present study which is focused on MoS₂ nanosheets grown on highly conductive porous MoO₂.

Molybdenum dioxide (MoO₂) with a distorted rutile structure is an unusual and attractive transition metal oxide

because of its low, metallic electrical resistivity ($8.8 \times 10^{-5} \Omega\cdot\text{cm}$ at 300 K in bulk samples), high melting point, and high chemical stability.²¹ Mesoporous crystalline MoO_2 materials have been prepared as potential electrode materials in Li ion batteries.^{23, 24} Herein, porous MoO_2 were synthesized by calcination at elevated temperatures using phosphomolybdic acid as a precursor and porous silica SBA-15 as a hard template, which exhibited high electrical conductivity and a large surface area. Subsequent sulfuration treatment led to the transformation of the top layers into MoS_2 nanosheets. The structures of the resulting $\text{MoS}_2/\text{MoO}_2$ nanocomposites were then characterized by various microscopic and spectroscopic measurements. Electrochemical measurements showed that the $\text{MoS}_2/\text{MoO}_2$ nanocomposites exhibited apparent HER activity with a low overpotential of -104 mV and robust electrochemical durability.

Experimental section

Synthesis of Porous Metallic MoO_2

Mesoporous silica SBA-15 and porous metallic MoO_2 were prepared by following literature protocols.^{24,25} In a typical experiment, SBA-15 (1.0 g) was mixed with phosphomolybdic acid ($\text{H}_3\text{PMo}_{12}\text{O}_{40}$, 4.2 g) in ethanol (15 mL) at room temperature under stirring in an open crucible. After the evaporation of ethanol, yellow powders were obtained and loaded on a quartz boat and heated to 500°C in a tube furnace at a heating rate of $2^\circ\text{C}/\text{min}$ under an atmosphere of 10% H_2 and 90% Ar. The heating was maintained at this temperature for 5 h. The obtained $\text{MoO}_2/\text{SBA-15}$ composite was treated by 60 mL of a 4% HF aqueous solution to remove the silica template, affording porous MoO_2 .

Synthesis of MoS_2 nanosheets supported on porous metallic MoO_2 ($\text{MoS}_2/\text{MoO}_2$)

MoS_2 nanosheets supported on mesoporous metallic MoO_2 were prepared by a simple hydrothermal process. In a typical experiment, 50 mg of porous MoO_2 obtained above and 150 mg of thioacetamide (TAA) were dissolved in 40 mL of water. The solution was then transferred to a 50 mL Teflon-lined stainless steel autoclave and heated in an electric oven at 200°C for 6 h, 12 h, 24 h or 48 h. The autoclave was naturally cooled to room temperature and the obtained $\text{MoS}_2/\text{MoO}_2$ composites were washed with distilled water, and dried at 80°C for 12 h, which were denoted as $\text{MoS}_2/\text{MoO}_2\text{-}x$ ($x = 6 \text{ h, 12 h, 24 h or 48 h}$). For comparison, pure MoS_2 nanosheets were also prepared in a similar fashion but without the MoO_2 scaffold. Experimentally, 30 mg of sodium molybdate ($\text{Na}_2\text{MoO}_4\cdot 2\text{H}_2\text{O}$) and 60 mg of thioacetamide ($\text{C}_2\text{H}_5\text{NS}$) were dissolved in 20 mL of deionized water to form a transparent solution. The solution was transferred to a Teflon-lined stainless steel autoclave and then heated in an electric oven at 200°C for 24 h. Pure MoS_2 nanosheets, as a black product, were harvested after the solution was centrifuged and then dried at 50°C for 12 h.

Characterizations

Field-emission scanning electron microscopic (FESEM, Model JSM-7600F) measurements were employed to characterize the morphologies of the obtained samples. Transmission electron microscopic (TEM) measurements were carried out with a JOEL JEM 2100F microscope. Powder X-ray diffraction (XRD) and small-angle XRD patterns of the samples were recorded with a Bruke D8 Advance powder X-ray diffractometer with $\text{Cu K}\alpha$ ($\lambda = 0.15406 \text{ nm}$) radiation. X-ray photoelectron spectroscopic (XPS) measurements were performed using an ESCALAB 250. Raman spectra were recorded on a RENISHAW inVia instrument with an Ar laser source of 488 nm in a macroscopic configuration. The BET surface area was characterized by Micromeritics ASAP 2010 with nitrogen adsorption at 77 K and the Barrett-Joyner-Halenda (BJH) method.

Electrochemistry

Electrochemical measurements were performed with an electrochemical workstation (Solartron Analytical 1287+1260) in a 0.5 M H_2SO_4 aqueous solution. A saturated calomel electrode (Hg/HgCl_2 in saturated KCl) and a platinum wire were used as the reference and counter electrode, respectively. A calculated amount of MoS_2 , MoO_2 , or $\text{MoS}_2/\text{MoO}_2$ was loaded on a glassy carbon electrode which was used as the working electrode. Experimentally, 4 mg of the respective catalyst powders was dispersed in 1 mL of 4:1 (v/v) water/ethanol mixed solvents with 40 μL of a Nafion solution under ultrasonication for 30 min. 4 μL of the resulting solution was dropcast onto the glassy-carbon disk by a microliter syringe and dried at room temperature. The catalyst loadings were all $0.22 \text{ mg}/\text{cm}^2$.

Polarization curves were acquired by sweeping the potential from 0 to -0.8 V (vs. SCE) at a potential sweep rate of $5 \text{ mV}/\text{s}$, with ohmic losses compensated electronically.²⁶ The accelerated stability tests were performed in 0.5 M H_2SO_4 at room temperature by potential cycling between $+0.1$ and -0.5 V (vs. SCE) at a sweep rate of $100 \text{ mV}/\text{s}$ for a given number of cycles. Current-time responses were monitored by chronoamperometric measurements for up to 10 h. Hydrogen production at the $\text{MoS}_2/\text{MoO}_2$ modified glassy carbon electrode was carried out at -0.5 V (vs. SCE).

In all measurements, the SCE reference electrode was calibrated with respect to a reversible hydrogen electrode (RHE). The calibration was performed in a high-purity H_2 (99.999%) saturated electrolyte with two Pt wires as the working electrode and counter electrode, respectively. Cyclic voltammograms (CVs) were acquired at the scan rate of $1 \text{ mV}/\text{s}$, and the average of the two potentials at which the current crossed zero was taken as the thermodynamic potential for the hydrogen electrode reactions. In 0.5 M H_2SO_4 , $E_{\text{SCE}} = E_{\text{RHE}} + 0.273 \text{ V}$.

Results and discussion

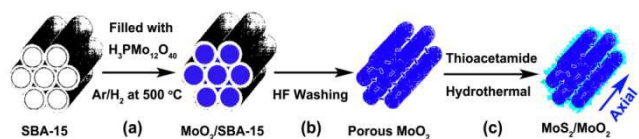


Figure 1. Schematic of the synthesis of MoS₂ nanosheets supported on porous metallic MoO₂ (MoS₂/MoO₂).

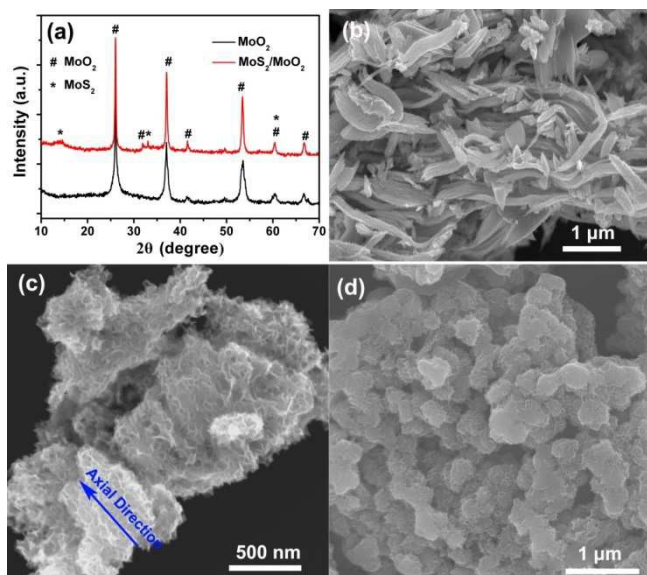


Figure 2. (a) XRD of MoO₂ and MoS₂/MoO₂-6h, (b) representative SEM image of MoO₂, (c) side-view and (d) top-view SEM images of MoS₂/MoO₂-6h.

Figure 1 describes the procedure for a typical synthesis of MoS₂/MoO₂ nanocomposites, which involves three major steps: (a) molecular sieves (SBA-15) were filled with phosphomolybdic acid, then calcined under a 10% H₂/90% Ar atmosphere to synthesize MoO₂/SBA-15 by the decomposition of phosphomolybdic acid; (b) HF was used to remove the SBA-15 template and obtain one-dimensional porous MoO₂; (c) hydrothermal reaction of porous MoO₂ with TAA led to the transformation of the top layers of MoO₂ into MoS₂ nanosheets forming MoS₂/MoO₂ composites.

The as-prepared samples were firstly characterized by using XRD measurements. From Figure 2a, one can see that for the MoS₂/MoO₂-6h sample (red curve), the main crystalline phase is MoO₂ (JCPDS: 32-0671, Monoclinic, *a* = 0.56 nm, *b* = 0.48 nm, *c* = 0.55 nm), with characteristic diffraction peaks at 26.0° (011), 31.8° (101), 36.9° (111), 41.5° (120), 53.3° (112), 60.2° (031) and 66.5° (131), which are all well-defined also with the MoO₂ sample (black curve). Several weak diffraction peaks can also be seen at 14.5°, 33.0°, and 60.4° that are consistent with MoS₂ (003), (101), and (113) crystalline planes, respectively (JCPDS: 65-3656, Hexagonal, *a* = *b* = 0.32 nm, *c* = 1.8 nm). These results suggest the formation of MoO₂/MoS₂ composites. The XRD patterns of MoS₂/MoO₂ composites prepared for other hydrothermal reaction times (up to 48 h) were shown in Figure S1. It can be seen that in all samples, MoO₂ remained as the primary crystalline phase, along with weak diffraction peaks of MoS₂, suggesting that only the top layers of MoO₂ were chemically transformed into MoS₂ under hydrothermal

conditions. The formation of MoS₂ was further confirmed in Raman spectroscopic measurements (Figure S2) which exhibited a series of vibrational bands at 120, 141.6, 192, 281, 333.4, and 374.2 cm⁻¹ that are characteristic of MoS₂.²⁷ The MoO₂ vibrational bands are also well-defined at 817.3 and 990.7 cm⁻¹.^{19, 23, 28}

SEM measurements were then carried out to examine the surface morphologies. Figure 2b depicts an overview of the porous one-dimensional MoO₂ nanostructures with 200–300 nm in width and 1–3 μm in length, consistent with the dimensions of SBA-15 (Figure S3). After hydrothermal treatment with TAA for 6 h, it can be seen that the MoO₂ surfaces were decorated with a number of curvy nanosheets, as evidenced in SEM images in Figure 2c (side view) and 2d (top view along axial direction), which were most likely MoS₂ nanosheets. This is consistent with the XRD results. The mesoporous structure of the MoS₂/MoO₂-6h composites was further confirmed by nitrogen adsorption/desorption measurements which featured a typical type-IV isotherm (Figure S4). However, because of the high molecular weight of MoO₂ and MoS₂, the MoS₂/MoO₂-6h composites showed only a relatively low specific surface area of 34.58 m²/g.

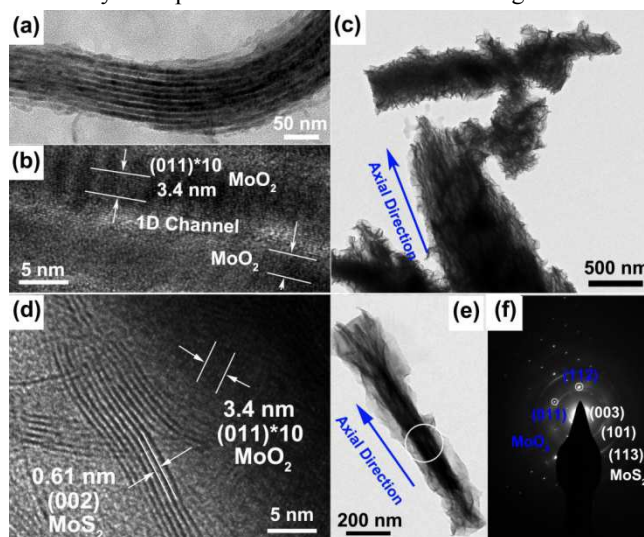


Figure 3. TEM images of (a, b) porous MoO₂ and (c-e) MoS₂/MoO₂-6h; (f) selected area electron diffraction patterns of MoS₂/MoO₂-6h.

Mesostructures with regular spacing are well-defined in TEM measurements, as depicted in Figure 3. From panel (a), it can be seen that the obtained porous MoO₂ displayed one-dimensional channels of 3 to 4 nm in diameter and 5 to 6 nm in wall thickness throughout the entire particle domain, indicating that porous MoO₂ was essentially grown on the internal surface of SBA-15 (Figure S5). The corresponding small-angle XRD patterns (Figure S6) suggest a consistent periodic mesostructure. Furthermore, from the high-resolution TEM image in Figure 3b the interlamellar spacings can be estimated to be 0.34 nm which is consistent with MoO₂ (011). After hydrothermal treatment with TAA for 6 h, it can be seen that the MoO₂ surface was extensively roughened where the sheet-like structures were most likely MoS₂ (Figure 3c). From Figure

3d, two interlamellar spacings can be identified. One is 0.61 nm that might be ascribed to MoS₂ (002), consistent with the XRD results in Figure 2a, and other is 0.34 nm for MoO₂ (011). Interestingly, the MoS₂ nanosheets were mostly aligned perpendicular to the surface of one-dimensional MoO₂, exposing abundant folded edges that are known to exhibit high catalytic activity for HER.^{29,30} Selected area electron diffraction studies were then carried out with a MoS₂/MoO₂-6h bundle (Figure 3e), and the patterns in Figure 3f display concentric rings that might be assigned to MoS₂ (003), (101), and (113), and diffraction spots for MoO₂ (112) and (011), respectively, indicating that the prepared nanocomposites were indeed composed of monocrystalline MoO₂ and polycrystalline MoS₂.

XPS measurements were then carried out to further investigate the chemical composition and valence states of the samples, which were shown in Figure 4. From the survey spectra in panel (a), the elements of Mo, S, O and C can be clearly identified. The C element shows a major peak at 284.5 eV that is characteristic of sp² C (Figure 4b). Figure 4c depicts the high-resolution scans of the Mo3d electrons with two major peaks at 229.6 eV and 232.8 eV, consistent with Mo3d_{3/2} and 3d_{5/2} for MoO₂ and MoS₂, respectively.^{19, 31} The shoulder at 235.4 eV is likely due to the existence of a small amount of Mo⁶⁺.³²⁻³⁴ Meanwhile, the S2p electrons exhibited various bonding energies for S²⁻ (162.4 eV, 163.7 eV, 164.9 eV, and 226.9 eV), as shown in Figure 4c and 4d.

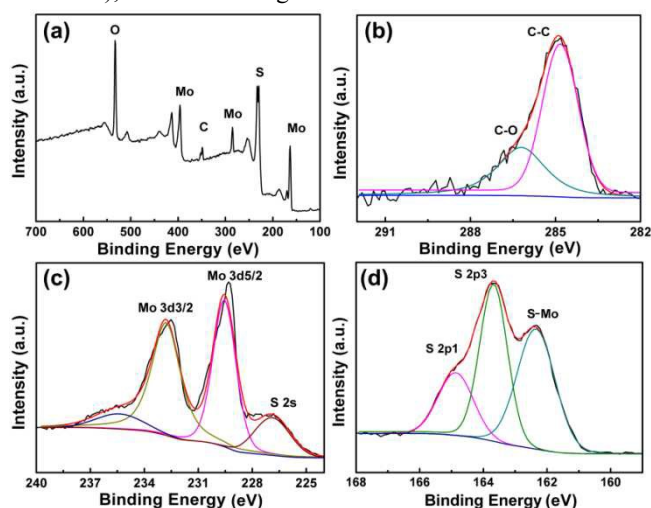


Figure 4. (a) XPS survey spectra and high-resolution scans of (b) C1s, (c) Mo3d and (d) S2p electrons of MoS₂/MoO₂-6h. Black curves are experimental data and colored curves are deconvolution fits.

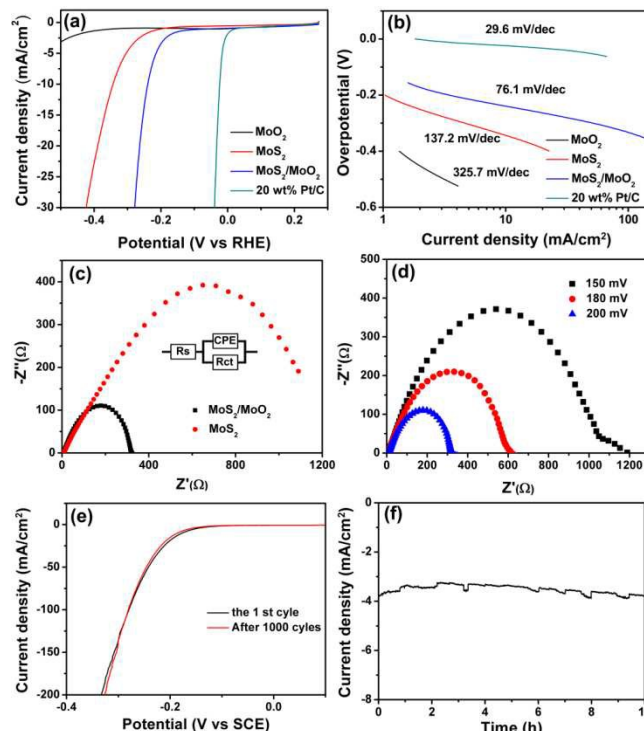


Figure 5. (a) Polarization curves for HER in 0.5 M H₂SO₄ on a glassy carbon electrode modified with MoO₂, MoS₂, MoS₂/MoO₂-6h and 20 wt% Pt/C, respectively. Potential sweep rate 5 mV/s. (b) Corresponding Tafel plots (overpotential versus log current density) derived from (a). (c) Nyquist plots and the equivalent circuit of MoS₂ and MoS₂/MoO₂-6h at the potential of -200 mV (vs RHE). (d) MoS₂/MoO₂-6h at various HER overpotentials in 0.5 M H₂SO₄. (e) HER polarization curves for MoS₂/MoO₂-6h before and after 1000 cycles of potential sweeps. (f) Current-time plots of the MoS₂/MoO₂-6h electrode at the applied potential of -0.23 V (vs RHE).

The electrocatalytic activities for HER of the samples prepared above were then examined by electrochemical measurements in 0.5 M H₂SO₄. From Figure 5a, it can be seen that MoO₂ exhibited poor catalytic activity for HER, with almost no reduction currents until the electrode potential was more negative than -0.4 V (black curve). In sharp contrast, apparent non-zero cathodic currents can be seen at the electrode modified by MoS₂/MoO₂-6h (blue curve) with an onset potential of -0.104 V (vs. RHE) and a small Tafel slope of 76.1 mV/dec from panel (b). Such a performance is markedly better than that of pure MoS₂ (red curve, -188 mV, 137.2 mV/dec) at the same catalyst loading. At the same overpotential (-0.3 V), the current density of the MoS₂/MoO₂-6h electrode (-51.5 mA/cm²) was about 11 times higher than that of pure MoS₂ (-4.7 mA/cm²). In addition, one can see that the HER activity diminished somewhat with prolonging hydrothermal reaction time (Figure S7), possibly because of increasing charge transfer resistance with an increasing coverage of MoS₂ that is less conductive than MoO₂ (Figure S8). Yet, one may notice that the activity remains subpar as compared to that of commercial 20 wt % Pt/C catalysts (green curve, -0.01 V, 29.4 mV/dec).

Electrochemical impedance spectroscopy (EIS) is also a powerful technique in the characterization of interfacial reactions and electron-transfer kinetics in HER. Figure 5c and d

showed the representative Nyquist plots of the MoS₂/MoO₂-6h and MoS₂-modified glassy-carbon electrodes. More detailed analyses were carried out by fitting the impedance spectra to an equivalent circuit (Figure 5c inset), where a constant phase element (CPE) was employed. The charge transfer resistance (R_{ct}) of the MoS₂/MoO₂-6h electrode (148.5 Ω) was found to be markedly lower than that of pure MoS₂ (661.2 Ω), suggesting that the highly conductive MoO₂ substrates reduced the resistance of the composite catalysts of MoS₂/MoO₂-6h. In fact, from Figure S9, it can be seen that at the potential of -200 mV (vs. RHE), the series resistance (R_s) was reduced from 7.3 Ω for MoS₂ to 6.2 Ω for MoS₂/MoO₂-6h. In addition, from Figure 5d, it can be seen that R_{ct} of MoS₂/MoO₂-6h decreased significantly with increasing overpotentials, from 503.2 Ω at -150 mV to 148.5 Ω at -200 mV, as evidenced by the apparent shrinkage of the diameter of the semicircles. Additionally, R_{ct} was found to increase with prolonging hydrothermal reaction time, suggesting an increasing loading of MoS₂ nanosheets on the MoO₂ surface hindered charge transport (Figure S8).

In addition to good catalytic activity, the MoS₂/MoO₂ electrode also exhibited good stability for HER. Figure 5e shows that, after 1,000 potential cycles, the j-V curve of the MoS₂/MoO₂-6h electrode remained almost unchanged. To further investigate the stability of MoS₂/MoO₂-6h and MoO₂ in HER, the current-time plots at the applied potential of -0.23 V (vs. RHE) was collected and depicted in Figure 5f and Figure S10, respectively. It can be seen that the reduction currents remained almost invariant over 10 h of continuous operation, indicating excellent durability of the electrodes for HER in 0.5 M H₂SO₄. These behaviors are actually very similar to that of commercial 20 wt% Pt/C (Figure S11).

Experimentally, a number of bubbles were observed on the surface of the MoS₂/MoO₂-6h electrode (Figure S12a). The gas was confirmed to be hydrogen by gas chromatography measurements, and the rate of hydrogen production was estimated to be 120 mmol/g·h, as depicted in Figure S12b.

Such an HER performance of MoS₂/MoO₂ (onset overpotential -104 mV, Tafel slope 67.3 mV/dec) is better than or comparable to those of leading Mo-based HER catalysts, such as semimetallic MoS₂ ultrathin nanosheets (-130 mV, 69 mV/dec),³⁵ MoS₂ nanoflower-decorated reduced graphene oxide paper (-190 mV, 95 mV/dec),³⁶ and MoSe₂ nanosheets/graphene hybrids (-150 mV, 101 mV/dec)³⁷, but somewhat lower than that of WS₂ (-142 mV, 70 mV/dec)³⁸ and MoS_x/NCNT (-75 mV, 40 mV/dec)³⁹. This may be attributed to the following factors. The first is the high electronic conductivity of MoO₂ ($8.8 \times 10^{-5} \Omega \cdot \text{cm}$ at 300 K in bulk samples), as confirmed by electrochemical impedance spectroscopic measurements where the charge-transfer resistance of MoS₂/MoO₂ was markedly smaller than that of pure MoS₂ (Figure 5c). Second, the continuously interconnected pore structures of MoO₂ provided effective channels for mass transport. Third, the vertically aligned MoS₂ nanosheets offered abundant edge sites, leading to fast interdomain electron transport and high HER activity.

Conclusion

In this study, porous metallic MoO₂-supported MoS₂ nanosheets (MoS₂/MoO₂) were prepared by sulfuration treatments of porous MoO₂ where the top layers of MoO₂ were hydrothermally transformed into MoS₂. One-dimensional porous MoO₂ was prepared by calcination of phosphomolybdic acid using mesoporous silica (SBA-15) as the template. The charge transfer resistance of the MoS₂/MoO₂ nanocomposites in HER was found to be markedly lower than that of pure MoS₂, most likely because the highly conductive MoO₂ significantly reduced the resistance of the composite catalyst. Electrochemical studies showed that the obtained electrocatalysts exhibited excellent HER activity with an onset potential of -104 mV (vs RHE), a large current density (10 mA/cm² at -0.24 V), a small Tafel slope of 76.1 mV/dec and robust electrochemical durability. The HER performance might be ascribed to the high electrical conductivity and porous structure of MoO₂ that allowed for effective charge and mass transport.

Acknowledgments

This work was supported by the National Recruitment Program of Global Experts, the the PhD Start-up Funds of the Natural Science Foundation of Guangdong Province (S2013040016465), and Zhujiang New Stars of Science & Technology (2014J2200061).

Notes and references

^a New Energy Research Institute, College of Environment and Energy, South China University of Technology, Guangzhou Higher Education Mega Center, Guangzhou, Guangdong 510006, China
E-mail: eszhouwj@scut.edu.cn (W.J.Z.)

^b School of Materials Science and Engineering, South China University of Technology, Tianhe District, Guangzhou, Guangdong 510641, China


^c Department of Chemistry and Biochemistry, University of California, 1156 High Street, Santa Cruz, California 95064, United States
E-mail: shaowei@ucsc.edu (S.W.C.)

† Electronic Supplementary Information (ESI) available: XRD patterns, Raman spectra, TEM images and additional voltammetric data. See DOI: 10.1039/b000000x/

1. E. Anxolabéhère-Mallart, C. Costentin, M. Fournier, S. Nowak, M. Robert and J.-M. Savéant, *J Am Chem Soc* 2012, 134, 6104-6107.
2. R. Subbaraman, D. Tripkovic, D. Strmcnik, K.-C. Chang, M. Uchimura, A. P. Paulikas, V. Stamenkovic and N. M. Markovic, *Science*, 2011, 334, 1256-1260.
3. W. Zhou, X.-J. Wu, X. Cao, X. Huang, C. Tan, J. Tian, H. Liu, J. Wang and H. Zhang, *Energy Environ Sci*, 2013, 6, 2921-2924.
4. J. D. Benck, T. R. Hellstern, J. Kibsgaard, P. Chakthranont and T. F. Jaramillo, *ACS Catal*, 2014, 4, 3957-3971.
5. C. He, X. Wu, J. Shen and P. K. Chu, *Nano Lett*, 2012, 12, 1545-1548.
6. M. L. Helm, M. P. Stewart, R. M. Bullock, M. R. DuBois and D. L. DuBois, *Science*, 2011, 333, 863-866.

7. D. Gopalakrishnan, D. Damien and M. M. Shaijumon, *ACS Nano*, 2014, 8, 5297-5303.
8. M. S. Faber and S. Jin, *Energy Environ Sci*, 2014, 7, 3519-3542.
9. L. Cheng, W. Huang, Q. Gong, C. Liu, Z. Liu, Y. Li and H. Dai, *Angew Chem Int Ed* 2014, 53, 7860-7863.
10. Z. Xing, Q. Liu, A. M. Asiri and X. Sun, *Adv Mater*, 2014, 26, 5702-5707.
11. W. Zhou, K. Zhou, D. Hou, X. Liu, G. Li, Y. Sang, H. Liu, L. Li and S. Chen, *ACS Appl. Mater. Interfaces*, 2014, 6, 21534-21540.
12. D. V. Esposito, S. T. Hunt, A. L. Stottlemeyer, K. D. Dobson, B. E. McCandless, R. W. Birkmire and J. G. Chen, *Angew Chem Int Ed* 2010, 49, 9859-9862.
13. B. Hinnemann, P. G. Moses, J. Bonde, K. P. Jørgensen, J. H. Nielsen, S. Hørch, I. Chorkendorff and J. K. Nørskov, *J Am Chem Soc* 2005, 127, 5308-5309.
14. Y.-H. Chang, C.-T. Lin, T.-Y. Chen, C.-L. Hsu, Y.-H. Lee, W. Zhang, K.-H. Wei and L.-J. Li, *Adv Mater*, 2013, 25, 755-755.
15. X. Ge, L. Chen, L. Zhang, Y. Wen, A. Hirata and M. Chen, *Adv Mater*, 2014, 26, 3100-3104.
16. W. Zhou, Y. Zhou, L. Yang, J. Huang, Y. Ke, K. Zhou, L. Li and S. Chen, *J Mater Chem A*, 2015, 3, 1915-1919.
17. Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong and H. Dai, *J Am Chem Soc* 2011, 133, 7296-7299.
18. J. Xie, J. Zhang, S. Li, F. Grote, X. Zhang, H. Zhang, R. Wang, Y. Lei, B. Pan and Y. Xie, *J Am Chem Soc* 2013, 135, 17881-17888.
19. W. Zhou, D. Hou, Y. Sang, S. Yao, J. Zhou, G. Li, L. Li, H. Liu and S. Chen, *J Mater Chem A*, 2014, 2, 11358-11364.
20. D. Kong, H. Wang, J. J. Cha, M. Pasta, K. J. Koski, J. Yao and Y. Cui, *Nano Lett*, 2013, 13, 1341-1347.
21. D. B. Rogers, R. D. Shannon, A. W. Sleight and J. L. Gillson, *Inorg Chem*, 1969, 8, 841-849.
22. J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X. W. Lou and Y. Xie, *Adv Mater*, 2013, 25, 5807-5813.
23. J. Liu, S. Tang, Y. Lu, G. Cai, S. Liang, W. Wang and X. Chen, *Energy Environ Sci*, 2013, 6, 2691-2697.
24. Y. Shi, B. Guo, S. A. Corr, Q. Shi, Y.-S. Hu, K. R. Heier, L. Chen, R. Seshadri and G. D. Stucky, *Nano Lett*, 2009, 9, 4215-4220.
25. T.-W. Kim, F. Kleitz, B. Paul and R. Ryoo, *J Am Chem Soc* 2005, 127, 7601-7610.
26. M. Gong, Y. Li, H. Wang, Y. Liang, J. Z. Wu, J. Zhou, J. Wang, T. Regier, F. Wei, H. Dai, *J. Am. Chem. Soc.* 2013, 135, 8452-8455.
27. M. A. Lukowski, A. S. Daniel, F. Meng, A. Forticaux, L. Li and S. Jin, *J Am Chem Soc* 2013, 135, 10274-10277.
28. B. Windom, W. G. Sawyer and D. Hahn, *Tribol Lett*, 2011, 42, 301-310.
29. D. Y. Chung, S.-K. Park, Y.-H. Chung, S.-H. Yu, D.-H. Lim, N. Jung, H. C. Ham, H.-Y. Park, Y. Piao, S. J. Yoo and Y.-E. Sung, *Nanoscale*, 2014, 6, 2131-2136.
30. Y. Yan, X. Ge, Z. Liu, J.-Y. Wang, J.-M. Lee and X. Wang, *Nanoscale*, 2013, 5, 7768-7771.
31. W. Zhou, Z. Yin, Y. Du, X. Huang, Z. Zeng, Z. Fan, H. Liu, J. Wang and H. Zhang, *Small*, 2013, 9, 140-147.
32. J. D. Benck, Z. Chen, L. Y. Kuritzky, A. J. Forman and T. F. Jaramillo, *ACS Catal*, 2012, 2, 1916-1923.
33. L. Yuwen, F. Xu, B. Xue, Z. Luo, Q. Zhang, B. Bao, S. Su, L. Weng, W. Huang and L. Wang, *Nanoscale*, 2014, 6, 5762-5769.
34. Z. Chen, D. Cummins, B. N. Reinecke, E. Clark, M. K. Sunkara and T. F. Jaramillo, *Nano Lett*, 2011, 11, 4168-4175.
35. X. Sun, J. Dai, Y. Guo, C. Wu, F. Hu, J. Zhao, X. Zeng and Y. Xie, *Nanoscale*, 2014, 6, 8359-8367.
36. C.-B. Ma, X. Qi, B. Chen, S. Bao, Z. Yin, X.-J. Wu, Z. Luo, J. Wei, H.-L. Zhang and H. Zhang, *Nanoscale*, 2014, 6, 5624-5629.
37. H. Tang, K. Dou, C.-C. Kaun, Q. Kuang and S. Yang, *J Mater Chem A*, 2014, 2, 360-364.
38. M. A. Lukowski, A. S. Daniel, C. R. English, F. Meng, A. Forticaux, R. J. Hamers and S. Jin, *Energy Environ Sci*, 2014, 7, 2608-2613.
39. D. J. Li, U. N. Maiti, J. Lim, D. S. Choi, W. J. Lee, Y. Oh, G. Y. Lee and S. O. Kim, *Nano Lett*, 2014, 14, 1228-1233.

ToC Graph

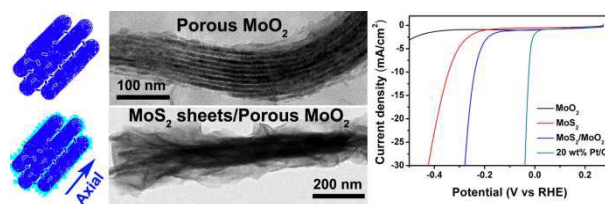

Porous metallic MoO₂-supported MoS₂ Nanosheets exhibited excellent electrocatalytic activity for HER and robust electrochemical durability.