

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Polyethyleneimine for copper absorption: kinetics, selectivity and efficiency in artificial seawater

Cite this: DOI: 10.1039/x0xx00000x

Johan B. Lindén,^a Mikael Larsson,^{a*} Bryan R. Coad,^b William M. Skinner^a and Magnus Nydén^a

Received 00th February 2014,

Accepted 00th April 2014

DOI: 10.1039/x0xx00000x

www.rsc.org/chemcomm


Polyethyleneimine (PEI) is known to bind copper ions effectively and selectively. However, this is the first report on PEI-based materials for copper scavenging from ultra-low concentrations in seawater matrixes. The findings are relevant for water purification and sensing applications as well as extraction of copper from oceans.

The importance of effective detection, separation and selective removal of transition metal ions from contaminated waters is growing due to their toxic effects.¹⁻⁴ Sources of contamination include metal plating, pickling in the steel industry, pigment industries and mining waste, to mention a few.⁵ In addition to the removal of metals from waste to meet regulations, recovery and reuse could offer economic benefits.⁶

There are also concerns about copper and zinc contamination passively released from antifouling paints in marinas and harbours.^{7,8} While the average copper concentration in seawater is around 3 ppb⁹, up to 22 and 114 ppb have been reported in a marina in San Diego Bay¹⁰ and coastal water of India¹¹, respectively.

Extraction of metals, especially uranium, from oceans has also attracted scientific interest over decades. Although the concentration of valuable metals in the oceans is typically very low, the vast abundance of water makes the total amount significant compared to minerals-based metals. The amount of energy needed to recover it seems, however, too high at present.¹²

Polyethyleneimine (PEI) polymers are well known for their ability to bind metal ions,^{13,14} with commercially available branched PEI commonly having primary, secondary and tertiary amine groups in approximately 1:1:0.7 ratio. The branched PEI is the most efficient in binding copper and forms complexes with a N:Cu ratio of 4-5.^{4,15} PEI covalently attached to silica particles, effectively removes copper from 6 ppm solutions at pH values ranging from 2-4.^{6,16} Similar materials were reported to remove copper from mine wastewater containing copper (130 ppm), aluminium (40 ppm), manganese (210 ppm) and zinc (550 ppm) with some selectivity at pH 5.⁵

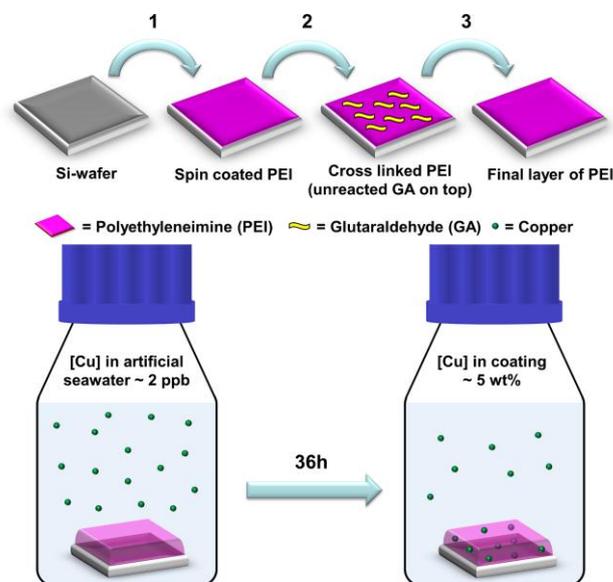

Scheme 1 Preparation of cross-linked PEI coatings and example of copper uptake from artificial seawater (for experimental details and calculations see S1 and S2 respectively, ESI†).

PEI has also been suggested for copper sensing applications.^{4,17,18} Wen et al. for instance developed a spectrophotometric method based on PEI in solution for binding Cu^{2+} with a detection limit of 566 nM (36 ppb) and high selectivity compared to a variety of transition metal ions.⁴ However, the method was not applicable for solutions at pH > 7. Moreover the effect of other metal ions was not investigated. Yuan et al., used hyperbranched PEI-coated silver nanoclusters together with a fluorescence quenching based technique to selectively detect copper.¹⁷ They reported an optimum selectivity at pH 4 and a detection limit of 10 nM (0.6 ppb) and reliable measurements over a wide pH range, varying ionic strength and temperatures. Like Wen et al.,⁴ the selectivity of copper was investigated for one metal ion at a time. To our knowledge no investigation has reported the effect of several

other metal ions competing with copper for binding to PEI at ppb concentrations.

Based on some of the results presented in this publication we recently patented an antifouling technique comprising a coating that selectively binds to a specific metal ion naturally abundant in an aqueous environment (international (PCT) patent application PCT/AU2013/001416). In addition to antifouling, the results presented below suggest that it might be feasible to remove copper contamination in harbours and marinas where the concentrations are above water quality criteria.¹⁰ For example, a copper contaminated marina located in southeastern San Diego bay contains 313000 m³ water with 22 ppb copper.¹⁰ With the technology presented here the concentration could be reduced, below chronic criteria (> 3.1 ppb) of the California Toxic Rule¹⁹, to 2 ppb (equivalent to a reduction of 6 kg) by using 137 kg of PEI (for calculations see S3, ESI†). Although it may be of interest to further indicate the feasibility of mining copper from the oceans by similar calculations, it is to the authors' beliefs that control of elevated concentrations in contaminated marinas comprises a more realistic application due to both energy requirements and abundance of copper.

In this work we used branched PEI (Mn ~ 60,000 and MW ~ 750,000) applied as very thin coatings on silicon wafers and subsequently cross-linked with glutaraldehyde (GA) by a method adapted from Tong *et al.*²⁰ (Scheme 1). The average dry layer thicknesses of the coatings were 7.9 nm (S.D. 1.1 nm, n = 32), as determined by ellipsometry (Table S2, ESI†). The coating thickness could be easily tuned by varying the concentration of PEI in solution used in the spin coating process (Table S3, ESI†). Only a slight increase in thickness was induced by GA crosslinking (Table S4, ESI†). The samples were further characterised by atomic force microscopy (AFM), revealing a smooth surface and providing a second measure of coating thickness that correlated well with ellipsometry (Fig. S2, ESI†).

Copper uptake started after immersing the coatings in artificial seawater or Milli-Q water, spiked with CuSO₄ to achieve copper concentrations in the range 2 to 200 ppb. The metal content in the coatings was determined by X-ray photoelectron spectroscopy (XPS) and reported as the relative metal to nitrogen ratio, as calculated from XPS survey spectra (e.g. Fig. 1). We are aware that other studies have measured the metal ion uptake indirectly in the water phase.^{5,6,16} Here a direct method was instead applied via XPS analysis to acquire the elemental composition throughout the coating. This was possible as the coatings were thinner than the maximum analysis depth of the XPS. The coating thickness also provided an advantageous timeframe for study of sorption equilibrium. Further analysis by XPS to determine the oxidation state of the copper ions in the coatings showed that the copper loaded coatings contained dominantly Cu(II) throughout the entire coating (Fig. S3 and Table S5, ESI†). The coatings were moreover shown to be stable through dry layer thickness determination before and after immersion in the different solutions (Table S6, ESI†). Shaking was shown to have insignificant effect on the copper uptake (Fig. S4, ESI†).

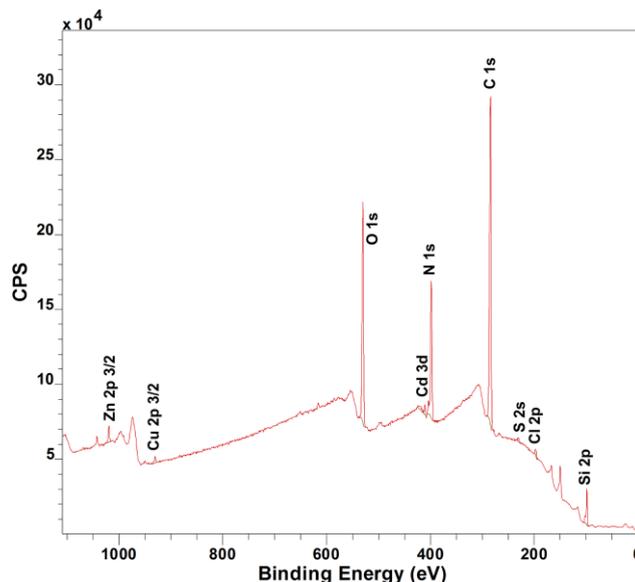


Fig. 1 Exemplifying XPS spectra of sample immersed for 15 minutes in artificial seawater (pH 8) with 12 different metal ions present at the same time: Al³⁺, Cd²⁺, Co²⁺, Cr³⁺, Cu²⁺, Fe²⁺, Mn²⁺, Mo⁶⁺, Ni²⁺, Pb²⁺, V³⁺, Zn²⁺. [Me²⁺] = 3 μM ([Cu²⁺] = 200 ppb). Quantified peak areas of the metals and nitrogen were used to determine the relative atomic ratio of metal to nitrogen in the coating (see S6 for further details, ESI†).

A plateau was reached after four hours of immersion in artificial seawater at 200 ppb (Fig. 2(a)). At that plateau the ratio of nitrogen to copper suggests a coordination number of 7.9 (S.D. 0.7, n = 3) which seems reasonable in comparison to the reported N:Cu ratio for PEI in solution of 4–5^{4,15}. The copper content in the coating was estimated to 13 wt% (for calculations see S2, ESI†). The sorption equilibrium was dependent of the concentration in solution and the solution volumes of the different concentrations were adjusted to contain the same excess of copper ions. For 20 ppb the plateau was reached after 12 hours and for 2 ppb the plateau was reached after 36 hours, where the copper content was estimated to 8 and 5 wt% respectively (for calculations see S2, ESI†).

Investigations of the metal ion uptake of the coatings from a mixture of twelve different metal ions revealed very high specificity for copper after long immersion times (Fig. 2(b)). At short immersion times the coatings contained more zinc and to some extent cadmium. Surprisingly no other metal ions were detected. This showed that the binding kinetics for zinc was faster but copper binding was thermodynamically favoured.

Comparison of the copper uptake in different solutions showed that when other metal ions were present the rate of copper uptake was slower than when only copper ions were present in both Milli-Q water and artificial seawater (Fig. 2(c)). This could also be an indication of a competitive binding-process taking place initially between copper, zinc and cadmium.

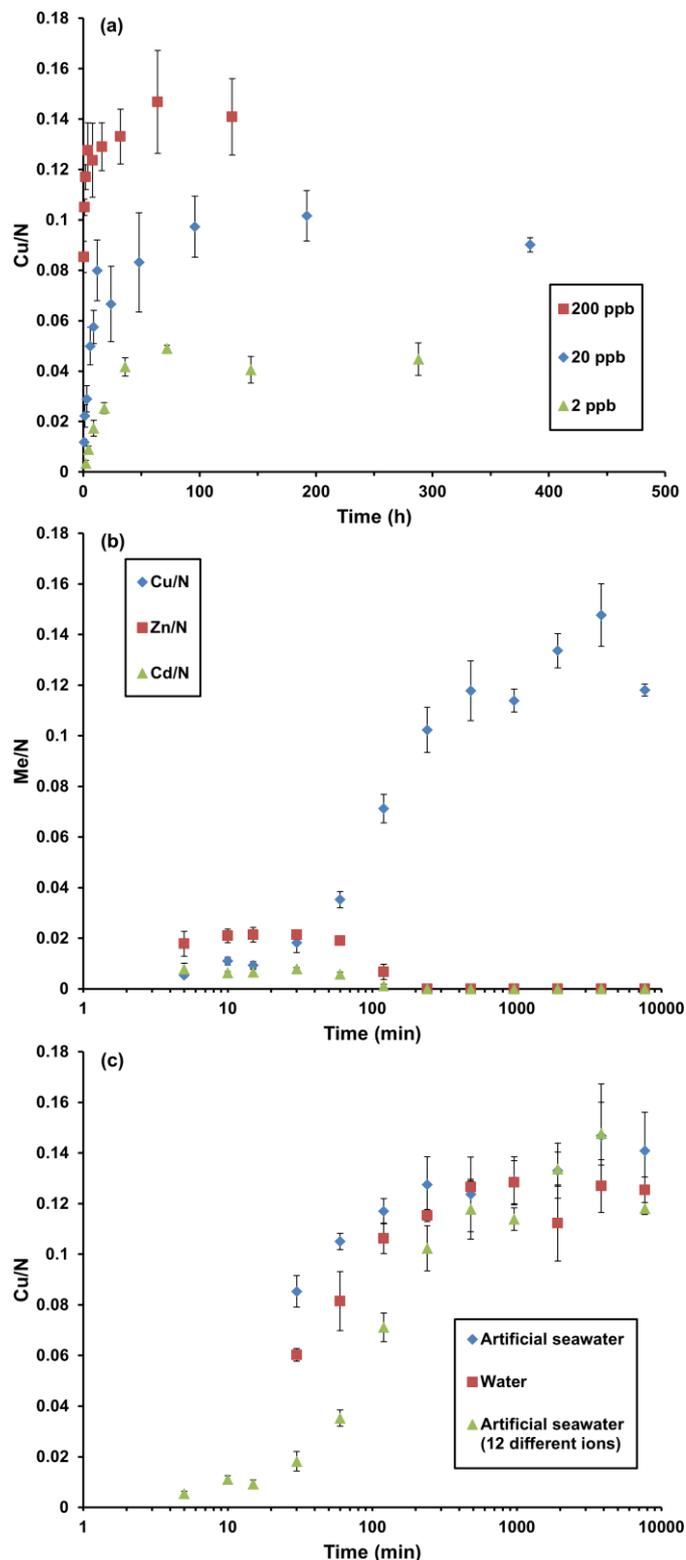


Fig. 2 Graphs showing metal uptake as of coatings over time. (a) Copper to nitrogen ratio as a function of time after immersion in artificial seawater (pH 8) for three different [Cu²⁺]. (b) Metal to nitrogen ratio as a function of time after immersion in artificial seawater (pH 8) with 12 different metal ions present at the same time: Al³⁺, Cd²⁺, Co²⁺, Cr³⁺, Cu²⁺, Fe²⁺, Mn²⁺, Mo⁶⁺, Ni²⁺, Pb²⁺, V³⁺, Zn²⁺. [Me²⁺] = 3 μ M ([Cu²⁺] = 200 ppb). (c) Copper to nitrogen ratio as a function of time after coating being immersed in different types of solutions. [Cu²⁺] = 200 ppb. Error bars indicate deviation (n=3).

In conclusion, thin coatings of chemically cross-linked PEI were shown to accumulate as much as 13, 8 and 5 wt% copper from 200, 20 and 2 ppb in artificial seawater, respectively. This makes PEI interesting for selective separation and purification as well as extraction of copper from oceans. From studies of mixtures of twelve transition metal ions, the coating was shown to be very specific towards copper after long immersion times. At short immersion times, the coatings contained more zinc. However, at longer times, zinc was replaced by copper, showing that the binding kinetics was faster for zinc, but with copper binding being thermodynamically favoured. Finally, it was shown that the rate of copper uptake was slower in the presence of other transition metal ions compared to neat copper in Milli-Q water or artificial seawater.

We acknowledge that this research has been financially supported by US DARPA (Grant number W911NF1310015) and ITEK Ventures Pty Ltd, the commercialisation arm of the University of South Australia. We also acknowledge that this work was performed in part at the South Australian node of the Australian National Fabrication Facility, a company established under the National Collaborative Research Infrastructure Strategy to provide nano and micro-fabrication facilities for Australia's researchers.

Notes and references

^a Ian Wark Research Institute, University of South Australia, Mawson Lakes, SA, 5095, Australia.

^b Mawson Institute, University of South Australia, Mawson Lakes, SA, 5095, Australia.

* E-mail: larsson.mikael@gmail.com; Fax: +61-8-830-23493 Tel: +61-8-830-23493

† Electronic Supplementary Information (ESI) available: Experimental details, calculations, table S1-S6 and Fig. S1-S4. See DOI: 10.1039/c000000x/

- P. E. Duru, S. Bektas, Ö. Genç, S. Patir and A. Denizli, *J. Appl. Polym. Sci.*, 2001, **81**, 197.
- E. Gaggelli, H. Kozłowski, D. Valensin and G. Valensin, *Chem. Rev. (Washington, DC, U. S.)*, 2006, **106**, 1995.
- N. G. Pekel, O., *Colloid Polym. Sci.*, 1999, **277**, 570.
- T. Wen, F. Qu, N. B. Li and H. Q. Luo, *Arab. J. Chem.*, 2013, <http://dx.doi.org/10.1016/j.arabjc.2013.06.013>.
- R. J. Fischer, D. Pang, S. T. Beatty and E. Rosenberg, *Sep. Sci. Technol.*, 1999, **34**, 3125.
- S. T. Beatty, R. J. Fischer, D. L. Hagers and E. Rosenberg, *Ind. Eng. Chem. Res.*, 1999, **38**, 4402.
- L. Kiaune and N. Singhasemanon, *Rev. Environ. Contam. Toxicol.*, 2011, **213**, 1.
- K. Schiff, D. Diehl and A. Valkirs, *Mar. Pollut. Bull.*, 2004, **48**, 371.
- R. R. Conry, in *Encyclopedia of Inorganic Chemistry*, John Wiley & Sons, Ltd, 2006, pp. 1.
- T. W. Biggs and H. D'Anna, *Mar. Pollut. Bull.*, 2012, **64**, 627.
- C. K. Sekhar, S. N. Chary, K. C. Tirumala and V. Aparna, *Acta Chim. Slov.*, 2003, **50**, 409.
- U. Bardi, *Sustainability*, 2010, **2**, 980.
- S. Kobayashi, K. Hiroishi, M. Tokunoh and T. Saegusa, *Macromolecules*, 1987, **20**, 1496.
- B. L. Rivas and K. E. Geckeler, in *Polymer Synthesis Oxidation Processes*, Springer, 1992, pp. 171.
- T. D. Perrine and W. R. Landis, *J. Polym. Sci. A-1 Polym. Chem.*, 1967, **5**, 1993.
- S. T. Beatty, R. J. Fischer, E. Rosenberg and D. Pang, *Sep. Sci. Technol.*, 1999, **34**, 2723.
- Z. Yuan, N. Cai, Y. Du, Y. He and E. S. Yeung, *Anal. Chem.*, 2013, **86**, 419.
- F. Ungaro, G. De Rosa, A. Miro and F. Quaglia, *J. Pharm. Biomed. Anal.*, 2003, **31**, 143.
- USEPA, California Toxics Rule, 40 CFR 131.38, Washington DC, 2013.
- W. Tong, C. Gao and H. Möhwald, *Polym. Adv. Technol.*, 2008, **19**, 817.