

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.


A Curing System of Benzoxazine with Amine: Reactivity, Reaction Mechanism and Material Properties

JiaQinSun^a, Wei Wei^a, YaZhenXu^a, JieHaoQu^a, XiangDong Liu^a and Takeshi Endo^b

^a Key Laboratory of Advanced Textile Materials and Manufacturing Technology, Ministry of Education, College of Materials and Textile, Zhejiang Sci-Tech University, Xiasha Higher Education Zone, Hangzhou 310018, P.R. China.

^b Molecular Engineering Institute, Kinki University, Kayanomori, Iizuka, 820-8555, Japan.

Graphical Abstract

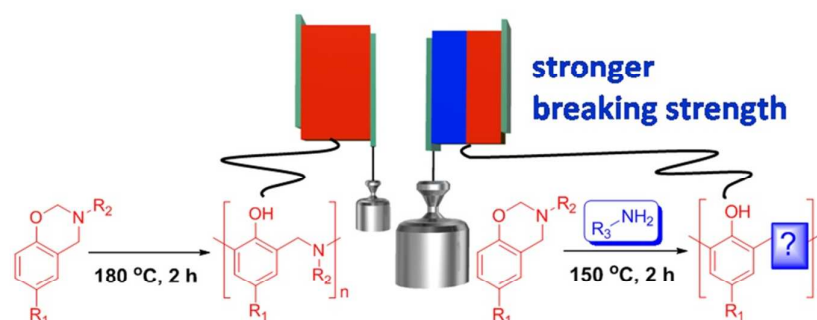

Not only the acceleration effect on curing, suitable amines react with benzoxazine, forming desired structures, and improving materials properties of the cured resins.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

A Curing System of Benzoxazine with Amine: Reactivity, Reaction Mechanism and Material Properties

JiaQin Sun^a, Wei Wei^a, YaZhen Xu^a, JieHao Qu^a, XiangDong Liu^{*a} and Takeshi Endo^b

Received (in XXX, XXX) XthXXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXXXX 20XX

DOI: 10.1039/b000000x

Five commercially available amines: m-phenylenediamine (A1), m-xylylenediamine (A2), isophorone diamine (A3), trimethylhexamethylenediamine (A4), and 4,4'-diaminodiphenyl sulfone (A5), were examined as a nucleophilic hardener for bis-benzoxazine monomers based on aniline paired with bisphenol-A (BA-a) or bisphenol-F (BF-a). The reactivity and reaction mechanism of their reactive mixture with BA-a were investigated using FTIR and NMR spectroscopy, DSC, and HPLC techniques. It is found that BA-a rapidly cured with amines upon heating at 120 °C or 150 °C, which the cure rate is similar to the amine/epoxy curing process in practical uses, and significantly faster than ring-opening polymerization of bulk BA-a. The possible reaction mechanism was supported by the experimental results and includes three successive steps: (i) nucleophilic substitution at the carbon atom (O-C-N) in the oxazine ring by the amine, (ii) thermal decomposition of the resulting aminomethanaminium structure, and (iii) electrophilic addition of the newly formed iminium ion with the aromatic ring to form stable aminomethylphenol structures. These findings are helpful to improve thermosetting resins in terms of their chemical structure, material properties, and processability.


1. Introduction

Since the discovery in 1994 that benzoxazines possess unique thermoset features that are better than conventional phenolic resins¹, this class of heterocyclic compounds has attracted great interest over the last 20 years²⁻⁵. When compared with other polymers, polybenzoxazines exhibit significant advantages due to their mechanical and thermal properties, chemical and thermal stabilities, dimensional invariability during polymerization, and low surface energy⁶. In particular, it is gradually recognized that the most important and attractive characteristic of polybenzoxazines is the extraordinary flexibility in their molecular design⁷. Benzoxazines are typically synthesized from phenol, amine, and formaldehyde via a Mannich reaction. Desired benzoxazines can be synthesized using specially selected phenol derivatives and primary amines. There have been a lot of successful reports on the development of benzoxazine monomers to improve material performance or expand the range of their applications⁸, for example, lowering the polymerization temperature by introducing hydroxyl^{9, 10}, acetylene^{11, 12}, N-allyl¹³, and carboxylic acid groups¹⁴ to benzoxazine compounds, increasing the cross-linking density by the incorporation of polymerizable groups¹⁵⁻¹⁷, improving flame retardancy by phosphorylation of the cured products¹⁸, and others¹⁹⁻³².


To cure 1,3-benzoxazines, thermally accelerated polymerization has been the main focus for most researchers for a long time. Although the polymerization mechanism is complex and still poorly understood, the cationic polymerization mechanism shown in Scheme 1a has been widely recognized^{19, 20, 33-35}. The basic

concept of the reaction mechanism is the protonation of the oxygen atom in the oxazine ring, followed by the formation of a zwitter iminium ionic structure, and its subsequent electrophilic substitution to the aromatic ring. Based on this point, several accelerators for the polymerization have been successfully developed³⁶⁻³⁸.

Besides this main methodology for curing benzoxazine monomers, another approach using ring-opening addition reactions, which is similar to curing epoxy with various hardeners, has recently attracted growing attention. The merits expected of this new strategy are the possibility to lower the curing temperature and the capability to further improve the materials performance by careful selection of the cross-linking reagents. To date, very few compounds, including phenolic compounds³⁹⁻⁴⁴, thiols⁴⁵⁻⁴⁹, benzimidazoles⁵⁰, benzoxazoles^{26, 51, 52}, chitosan ammonium⁵³, and some polymers containing aromatic

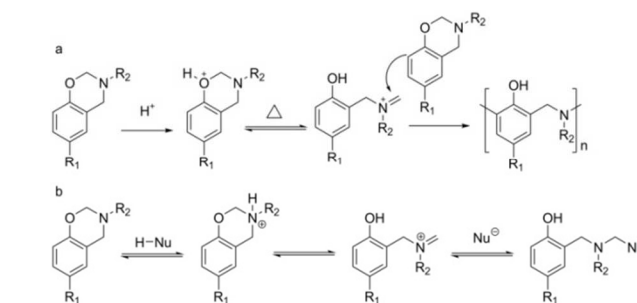

Scheme 1 The polymerization mechanisms of benzoxazine proposed by previous reports.

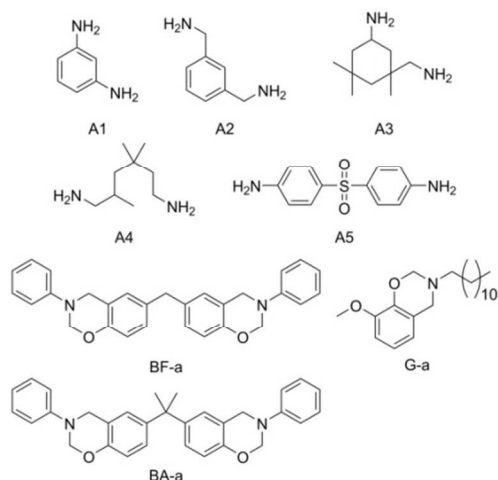

Scheme 2 The amines and benzoxazine monomers tested in the present work.

structures^{19, 21, 23}, have been reported to construct
 5 chemically linkages with benzoxazines. A ring-opening addition
 reaction mechanism has been extended from the cationic
 polymerization mechanism mentioned above to explain the
 reactions (Scheme 1b). The hardeners donate a proton to the
 benzoxazine, resulting in an anion to attack the electrophilic
 10 iminium intermediate. Clearly, the benzoxazine acts as a
 nucleophile towards the proton in this case and the lone pair of
 the nitrogen in the oxazine ring is thought to be the most reactive
 position. On the other hand, it is not unreasonable to suppose that
 the benzoxazine acts as an electrophile due to the electron-
 15 deficient carbon atom found between the nitrogen and oxygen
 (O-C-N) and that the six-membered heterocycle has an irregular
 chair structure with considerable ring strain⁵⁴. Therefore, it is
 expected that a variation of reactants can open the oxazine ring
 via a nucleophilic attack to the electrophilic portion at the C8
 20 carbon atom.

In this study, five commercially available amines: m-
 phenylenediamine (A1), m-xylylenediamine (A2), isophorone
 diamine (A3), trimethylhexamethylenediamine (A4), and 4,4'-
 diaminodiphenyl sulfone (A5), which are often used as industrial
 25 hardener for epoxy resins, are selected as the nucleophilic
 reactants to harden benzoxazines (Scheme 2). Their reactivity
 with benzoxazine monomers was investigated using DSC and
 gel-point time analyses, and the reaction mechanism studied
 using NMR and FTIR spectroscopy, HPLC and reaction
 30 activation energy (E_a) analyses. The general properties of the
 amine-cured polybenzoxazine resins including their mechanical
 properties and thermal stability were also evaluated.

2. Experimental Section

2.1. Materials.

35 The amines and benzoxazines used in the present work
 were listed in Scheme 2. m-Phenylenediamine (A1), m-
 xylylenediamine (A2), isophorone diamine (A3),
 trimethylhexamethylenediamine (A4), 4,4'-diaminodiphenyl
 sulfone (A5), 2,2-Bis(4-hydroxyphenyl) propane (Bisphenol A),
 40 aniline, paraformaldehyde, guaiacol, lauramine,
 paraformaldehyde, formaldehyde (37 wt % in water), 1,6-

hexamethylenediamine (HMA), and benzylamine were purchased
 from Aladdin Reagent Co. (Shanghai, China). Bisphenol F based
 benzoxazine (BF-a, 75 wt % in butanone) was obtained from
 45 Huntsman investment Co., Ltd (Utah, USA). All other chemicals
 are of analytical grade and were purchased from Hangzhou Mike
 Chemical Agents Co. Ltd (Hangzhou, China).

2.2. Measurements.

¹H-NMR spectra were recorded on an Avance AV-400 (400
 50 MHz) NMR spectrometer (Bruker Co., Switzerland) in CDCl₃ or
 DMSO with TMS as an internal standard. FTIR spectra were
 taken on a Nicolet 5700 FT-IR plus spectrometer (Nicolet
 Company, Madison, USA). UV-vis absorption spectra were
 measured on an UV-2550 spectrophotometer (Shimadzu Co.,
 55 Japan). Viscosity was measured with a Brookfield CAP 2000+
 viscometer, which can offer high shear rate with integrated
 temperature control for test.

An Agilent 1100 HPLC system (Agilent Technologies Co., Ltd,
 USA) with an Agilent ZORBAX-SBC18 (150×4.6 mm) column
 60 and a UV detector operating at 254 nm were used for all HPLC
 measurements. HPLC buffer A is 5 mM sodium phosphate
 aqueous solution mixed with phosphoric acid (NaH₂PO₄/
 Na₂HPO₄ = 1/1 in mol), and HPLC buffer B is pure acetonitrile.
 The eluting flow rate was 1 mL/min. The linear gradient used was
 65 from 20 % to 95 % buffer B for 15 minutes.

DSC data were obtained from a DSC-1 differential scanning
 calorimeter (Mettler-Toledo corp., Switzerland) at a heating rate
 of 10 °C/min in a nitrogen flow (35 mL/min). TGA data were
 obtained from a TGA thermo-gravimetric analyzer (Mettler-
 70 Toledo corp., Switzerland) at a heating rate of 20°C/min under
 nitrogen atmosphere.

Mechanical tensile properties of the cured samples bound
 between aluminium sheets (bond surface area: 1.0 cm x 2.0 cm;
 binding thickness: fixed by glass beads of 0.2 mm diameter) were
 measured by an Instron-3367 instrument (Instron Co., Ltd, USA)
 75 (temperature, 25 °C; humidity, 30 %; speed, 10
 mm/min). Dynamic mechanical analysis (DMA) was performed
 with a TA Instruments Q800 DMA (USA) with a heating rate of
 5 °C/min from 25 to 250 °C at 1 Hz. Samples of 4 mm width
 80 were cut from films with approximate thickness of 0.4 mm.

2.3. Synthesis of 6,6'-(propane-2,2-diyl)bis-(3-phenyl-3,4-dihydro-2H-1,3-benzoxazine (BA-a)).

The mixture of aniline (18.80 g, 0.20 mol), paraformaldehyde
 (12.00 g, 0.40 mol), and bisphenol A (22.80 g, 0.10 mol) was
 85 stirred at room temperature for 15 min, heated at 100 °C for
 30min until the mixture became transparent. The pressure was
 reduced at 0.01 MPa for 30 min to remove the byproduct of water,
 cooled to 25 °C, dissolved in ethyl ether (100 mL) and washed
 with NaOH solution (3.00 M, 3x100 mL) and water (3x100 mL).
 90 The organic phase was added with anhydrous MgSO₄ (20.0 g),
 filtered, and dried under vacuum to obtain BA-a as a light yellow
 solid. Yield = 91 %; mp 61 °C; ¹H-NMR (CDCl₃) 6.71–7.26,
 5.33, 4.58, and 1.57 ppm; FTIR (KBr) 1328, 1230, 1157, 1030,
 and 946 cm⁻¹.

2.4. Synthesis of 3-dodecyl-8-methoxy-3,4-dihydro-2H-1,3-benzoxazine (G-a).

Laurylamine (4.63 g, 5.00 mmol) was dissolved in anhydrous

ethanol (10.00 mL), slowly added with formaldehyde solution (3.75 mL, 50.00 mmol), and stirred for 20 min. Guaiacol (3.11 g, 25.00 mmol) was added to the mixture, stirred for 15 min, heated at reflux for 7 h, recrystallized from ethanol, and dried under vacuum to obtain G-a as a white powder. Yield = 85 %; mp 50 °C; ¹H-NMR (CDCl₃) 6.57–6.83, 4.96, 4.00, 3.87, 2.76, 1.25–1.57, and 0.88 ppm; FTIR (KBr) 1331, 1224, 1138, 1033, and 935 cm⁻¹.

2.5. General formulation of the benzoxazine/amine curing systems.

BA-a (0.92 g, 2.00 mmol) and equivalent molar amount of the amine were dissolved in chloroform (for A1–A4, 2.0 mL) or a mixed solvent of chloroform and ethanol (1/1, v/v, for A5, 4.0 mL), and dried under vacuum to obtain uniform powder. These mixtures were employed as the samples for DSC, FTIR, TGA, and viscosity (redissolved in 3.0 mL of nitrobenzene) tests.

G-a (0.15 g, 0.50 mmol) and equivalent molar of benzylamine were dissolved in deuterated DMSO (6.0 mL), heated at 100 °C for a certain time, quenched with liquid nitrogen, and sampled for NMR analyses. These sample mixtures above (0.10 mL) were volumetrically fed to 10 mL with methanol, and subjected to the HPLC measurements to detect unreacted benzylamine molecules.

The BF-a solution and equivalent molar amount of the amine (A1–A5) were mixed (3 min) and degassed (3 min) with a conditioning mixer (AR-100, Thnky, Japan). Two pieces of filter paper (with an average pore size of 18 μm) were dipped in the BF-a/amine mixtures, clamped using polyimide sheets, dried under vacuum to remove the solvent, and cured at 120, 150, and 180 °C for 2 h, respectively. The resulted composite samples were subjected to DMA tests.

3. Result and Discussion

3.1. Reactivity of amines toward benzoxazine

BA-a/A1 mixtures with a variety of molar ratios were tested using DSC at a heating rate of 10 °C/min under a nitrogen atmosphere. The incorporation of A1 leads to considerable exothermic peaks (Fig. SI 1) at low temperature ranging from 100 to 200 °C. Because the ring-opening polymerization of neat BA-a takes place at high temperature (>200 °C), these peaks suggest that BA-a reacts with the amine in different ways. To estimate the stoichiometry ratio of the reactants, we defined BA-a moles per one mol amine in the reactive mixtures as *nBp* to describe BA-a dosage, and calculated the enthalpy values of the peaks formed at <200 °C as Δ*H*. The relationship between the Δ*H* and *nBp* was displayed in Fig. 1. The maximum Δ*H* value was obtained when *nBp* was 1.0, meaning that one amine group approximately reacts with one oxazine ring.

Based on the roughly stoichiometric estimate, we sequentially investigated the curing reactions of five amines (Scheme 2) with equimolar BA-a using a dynamic DSC process from 50 to 300 °C. The DSC profiles are shown in Fig. 2 and the important data selected from the DSC tests summarized in Table 1. In contrast with the test of neat BA-a without amine, the addition of alkylamines A2, A3, and A4 results in two distinctively exothermic peaks before the last peak occurs. However, with arylamines A1 and A5 only one peak was distinguishable to the control test. The next notable fact was that the peak temperatures of the alkylamine mixtures were very low (centered at ~75 °C),

suggesting that the reaction between BA-a and the amines tested is active and rapid. In addition, calculation of the enthalpy values indicates that the amines are responsible for reduction in the reaction enthalpy values by a third. Therefore, several interesting deductions can be summarized from these DSC results: (1) there are at least two reaction mechanisms that dominate the curing process occurring at different stages; (2) the reactivity of the amines is determined by their chemical structures, i.e., alkylamines are generally more reactive than arylamines; and (3) the reaction of BA-a with amine is slightly exothermic in contrast to the large enthalpy value of the thermally induced ring-opening polymerization of bulk BA-a.

To compare the reactivity of the five amines, we further explored the increase in viscosity behaviour of the reactive BA-a/amine (1/1, mol/mol) mixtures using a Brookfield viscometer. The mixtures were isothermally cured at 120 °C and 150 °C, and their gel time points defined as the moment that the viscosity suddenly increases. The viscosity of a thermosetting system generally corresponds to the curing reaction rate and is often used as an index to analyse the kinetics of polymerization. As shown in Fig. 3 and Table SI 1, the five amines significantly accelerate

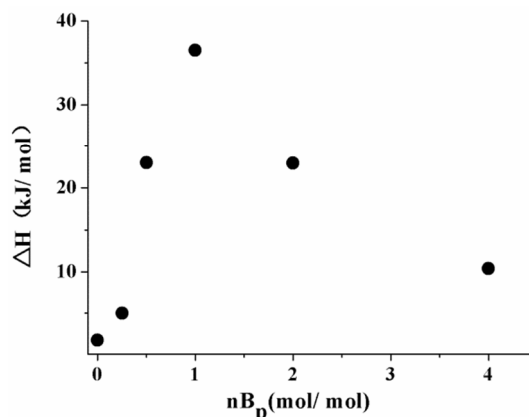


Fig. 1 Reaction enthalpy per mol of BA-a for the curing reaction with amine A1.

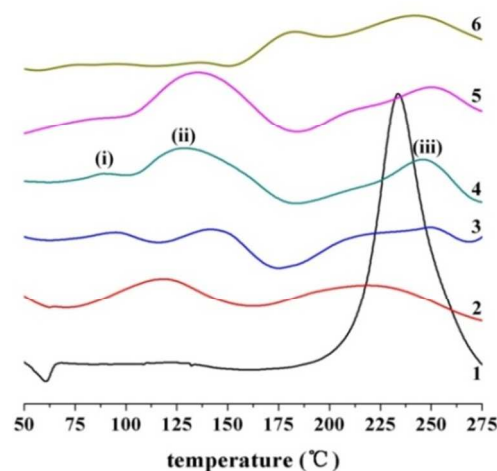


Fig. 2 DSC curves for BA-a without (1) and with amines A1 (2), A2 (3), A3 (4), A4 (5), and A5 (6).

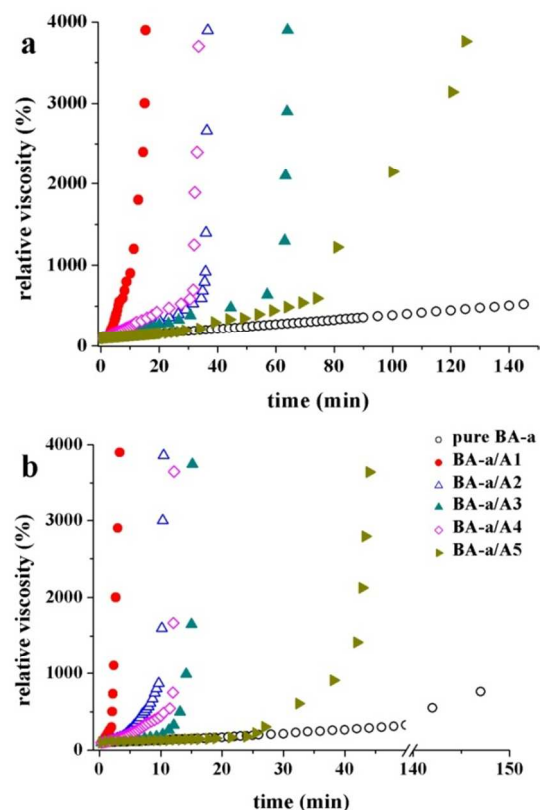


Fig. 3 The time dependence of viscosity during the isothermal curing of the reactive mixtures at (a) 120 °C and (b) 150 °C.

the curing reaction rate. In contrast with bulk BA-a, which shows little change in viscosity at the heating temperatures tested, the BA-a/amine mixtures display a rapid increase in viscosity ranging from minutes to hours. A comparison of A1 and A5 shows an obvious difference, which was attributed to the presence of the electron-withdrawing sulfone group in A5 decreasing the amine's reactivity towards BA-a.

3.2. Mechanical properties and thermal stability of the amine cured benzoxazine resins.

Based on the preliminary understandings gained on the reactivity of the benzoxazine/amine mixtures, we then paid attention to the mechanical and thermal properties of the thermosetting resins.

First, a series of the BA-a/amine cured resins binding two aluminum sheets were investigated under an initial strain rate of 10 mm/min. Table 2 summarizes the curing conditions, the engineering stress, and the stretch ratio for each mixture tested.

Table 1 Data from the dynamic DSC Measurements of the reactive BA-a/amine curing systems^a.

Curing System ^b	T ₀ (°C)	Peak 1 T _p (°C)	ΔH (J/g)	T ₀ (°C)	Peak 1 T _p (°C)	ΔH (J/g)	T ₀ (°C)	Peak 1 T _p (°C)	ΔH (J/g)
Pure BA-a	/	/	/	/	/	/	213	234	309
BA-a/A1	/	/	/	79	122	42	158	224	70
BA-a/A2	68	94	5	112	145	17	178	220	27
BA-a/A3	65	95	4	103	133	50	185	247	45
BA-a/A4	57	80	10	95	134	63	185	244	37
BA-a/A5	/	/	/	157	184	17	206	254	46

^a DSC data were obtained at a heating rate of 10 °C/min in nitrogen atmosphere.

^b BA-a/amines are in molar ratio of 1:1.

The comparison between the control tests, bulk BA-a cured via the different process, revealed that the ring-opening polymerization of BA-a needs high temperatures and long curing time. Conversely, the first three runs show that the addition of amine could simplify the curing process, in both the curing temperature and curing time. For example, the breaking strength of the second sample (run 2) that was cured within one hour is very close to that of the third sample (run 3), which can be recognized as a completely cured product. Moreover, the basicity of the amine seems to be an important factor to affect the mechanical's properties. This was reflected from the strength data obtained from the alkylamine samples (runs 5-7), which are significantly stronger than that of the arylamine samples (runs 4 and 8). It is noteworthy that the five amines can enhance the mechanical strength of the cured BA-a resins when compared with the control tests.

Next, DMA was used for the evaluation of the crosslinked polymers prepared from the heated BF-a/amine mixtures. As shown in Fig. 4a, the DMA curves indicated that the amine cured resins exhibit high storage modulus (ranged 3.5–6.5 GPa), which can be attributed to the high cross-linking of the curing system (Table S13). Compared to bulk BF-a, the amine cured resins except from amine A5 achieved approximately same storage modulus, and the amine A2 resulted a higher value of 6.5 GPa at 25 °C. The tan δ curves (Fig. 4b) of the amine cured resins showed the viscoelastic transition of the crosslinked polymers. Their glass transition temperatures (*T_g*) as defined by the tan δ peak presented interesting trends for the five amines. The arylamine samples (A1 and A5) have high *T_g* values (165–180 °C) similar to that of bulk BF-a, but the alkylamine cured resins show lower *T_g* values lesser than 105 °C. This fact is easy to understand as the rigid benzen rings limited the movement and rearrangement of the polymer chain segments.

Furthermore, the thermal stability of the cured thermosetting resins was investigated using TGA under nitrogen atmosphere. Fig. 5 and TableSI 2 show the TGA thermograms and data collected from these thermograms, respectively. The TGA profiles indicate that amines having aromatic structures (A1, A2, and A5) can increase the char yield at 800 °C. For instance, the BA-a/A1 resin reaches up to 43 %, which is clearly higher than that of neat polyBA-a (35 %). On the contrary, alkylamines (e.g., A3 and A4) decrease the char yield to ~20 %. This result may be attributed to the increased quantity from the aromatic rings.

Table 2 Breaking strength of the benzoxazine/amine bindings.

Runs	Amine/ Benzoxazine	Curing process	Breaking strength (Mpa)	Strain (%)
Control 1	--/BA-a	120 °C/2 h, 150 °C/2 h	18.53±3.93a	3.26±0.11
Control 2	--/BA-a	120 °C/2 h, 150 °C/2 h, 180 °C/2 h	53.01±13.68	4.96±0.72
1	A4/BF-a	120 °C/1 h	43.37±4.90	4.48±0.32
2	A4/BF-a	120 °C/0.5 h, 150 °C/0.5 h	139.16±21.06	5.63±0.99
3	A4/BF-a	120 °C/2 h, 150 °C/2 h, 180 °C/2 h	152.18±18.75	5.96±0.43
4	A1/BA-a	120 °C/2 h, 150 °C/2 h	48.29±10.97	4.42±0.28
5	A2/BA-a	120 °C/2 h, 150 °C/2 h	64.49±16.3	5.84±0.95
6	A3/BA-a	120 °C/2 h, 150 °C/2 h	128.57±37.33	8.51±2.51
7	A4/BA-a	120 °C/2 h, 150 °C/2 h	141.33±28.79	7.27±1.10
8	A5/BA-a	120 °C/2 h, 150 °C/2 h	55.38±9.19	3.26±0.11

^a the mean±SD, the average values were obtained from 5 tests..

Theoretically, aliphatic chains are easier to decompose into gaseous molecules such as ethylene when compared to aromatic rings. Interestingly, the addition of A5 resulted in improved thermal stability when compared to the neat polyBA-a resin. The main degradation of the A5-cured resin occurred at ~440 °C, while neat polyBA-a resin degrades at ~400 °C. However, in the case of alkylamines (A2, A3, and A4), the degradation temperature of the amine-cured resins were lower than that found with neat polyBA-a, implying that the aliphatic chains negatively affect the thermal stability of the thermoset resins.

3.3. Experimental observations associated with the reaction mechanism between the amine and benzoxazine.

The experimental data mentioned above demonstrates that the amines not only accelerate the benzoxazine curing process but also improve the mechanical or thermal properties of the cured

products. These results stimulated us to further study the possible reaction mechanism between benzoxazine and the amine.

Dynamic DSC scans were performed at four constant heating rates to investigate the five BA-a/amine curing systems. Table 3 summarizes their peak temperatures and their activation energy (*E_{ap}*) values calculated to characterize their reactivity. According to Kissinger's method^{55, 56} the relationship between DSC peak temperature *T_p* in K and the heating rate β is of the following form:

$$\ln(\beta/T_p^2) = \ln(AR/E_{ap} - E_{ap})/RT_p$$

where R is the gas constant, A is a frequency factor, and *E_{ap}* is the apparent activation energy. This equation allows calculation of *E_{ap}*/R from the slope of the linear plot of $\ln(\beta/T_p^2)$ vs. 1/*T_p*.

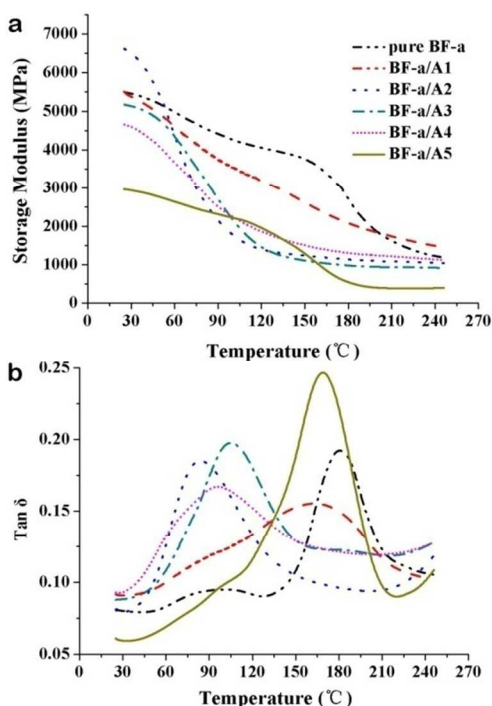


Fig. 4 DMA spectra of the amine-cured resins (cured at 120 °C/2 h, 150 °C/2 h, 180 °C/2 h). a, storage modulus; b, tan δ.

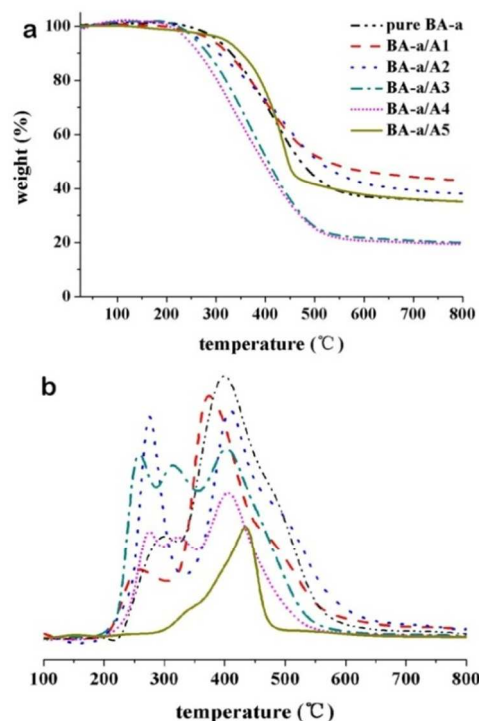
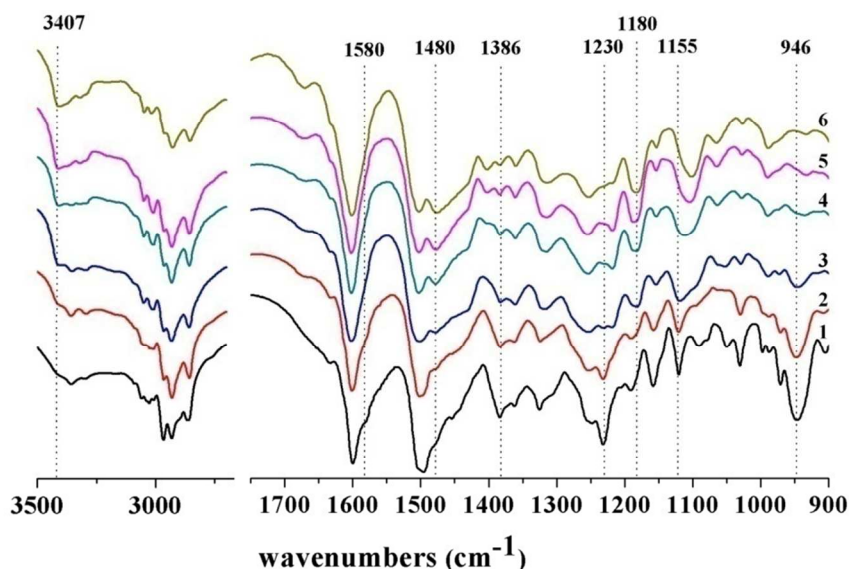


Fig. 5 TGA (a) and DTA (b) thermograms of the reactive mixtures cured at 180 °C.

Table 3 The activation energy (E_{ap}) data calculated by Kissinger's Method.

Curing System ^a	T_p (°C)				E_{ap} (KJ/mol)
	5 °C/min	10 °C/min	15 °C/min	20 °C/min	
Pure BA-a	227	234	245	252	106
BA-a/A1	115	122	129	135	84
BA-a/A2	131	145	150	156	74
BA-a/A3	124	133	141	148	73
BA-a/A4	123	134	142	153	59
BA-a/A5	177	184	189	200	96

^a BA-a/amines are in molar ratio of 1:1.**Fig. 6** FTIR spectra of the reactive BA-a/HMA mixture (1) heated at 100 °C for (2) 10, (3) 20, (4) 30, (5) 60, and (6) 90 min.

As shown in Table 3, the five benzoxazine/amine curing systems showed a lower E_{ap} value than that for the polymerization of pure BA-a. Their E_{ap} values follow an order of: arylamine > alicyclic amine > alkylamine, which is in good agreement with their basicity.

Then, we monitored the chemical changes of the BA-a/amine curing system with equivalent amounts using FTIR spectroscopy. 1,6-Hexamethylenediamine (HMA) was used as a replacement of amine A4 to simplify the IR spectrum, and the curing temperature was fixed at 100 °C to slow down the reaction rate. As shown in Fig. 6, the spectrum of the initial mixture without heating shows three characteristic peaks attributed to BA-a: the peak at 1230 cm^{-1} corresponds to the anti-symmetric stretching of the C–O–C bond in the oxazine ring, and the peaks at 1497 and 946 cm^{-1} are assigned to the trisubstituted benzene ring. In addition, the shoulder peak at 1580 cm^{-1} was assigned to the primary amine group of HMA. With the passage of cure time, the characteristic peaks of the reactants gradually decreased or shifted in the subsequent spectra. For example, three new and important peaks, corresponding to new covalent bonds, were observed at 1180, 1480, and 3407 cm^{-1} . They were attributed to C–N–H bond stretching of a secondary amine, the tetra-substituted aromatic ring and phenolic OH group, respectively. The FTIR spectroscopic evidence suggests that the reaction between the

amine and benzoxazine follows a ring-opening addition reaction mechanism.

The monofunctional benzoxazine, 3-dodecyl-8-methoxy-3,4-dihydro-2H-1,3-benzoxazine (G-a), was synthesized from guaiacol, laurylamine, and formaldehyde as described in our earlier reports^{57, 58}. The *ortho*- position on the phenolic ring is blocked and therefore complex polymerization can be avoided. Mixtures of G-a and benzylamine with an equivalent molar ratio were dissolved in deuterated DMSO and subjected to NMR spectroscopic analyses after heating for different times. As shown in Fig. 7, the ¹H NMR spectra of the mixtures reveal obvious signal changes in the methylene proton region ($\delta = 5.0$ –3.5 ppm). For benzoxazine, the resonances at $\delta = 3.89$ and 4.80 ppm were assigned to the –Ph–CH₂–N– (i') and –OCH₂–N– (ii') protons of the oxazine ring, respectively. In addition, the characteristic peak at $\delta = 3.71$ ppm is responsible to the methoxy group. The other reactant, benzylamine, gives a signal at $\delta = 3.74$ ppm (iii') corresponding to its methylene protons. Because the methoxy group attached to the benzene ring is chemically stable at the mild heating temperature of 100 °C, the peak at $\delta = 3.71$ ppm can be used as a reference for the other chemicals during the whole reaction process. After heating the mixture for a short time, a

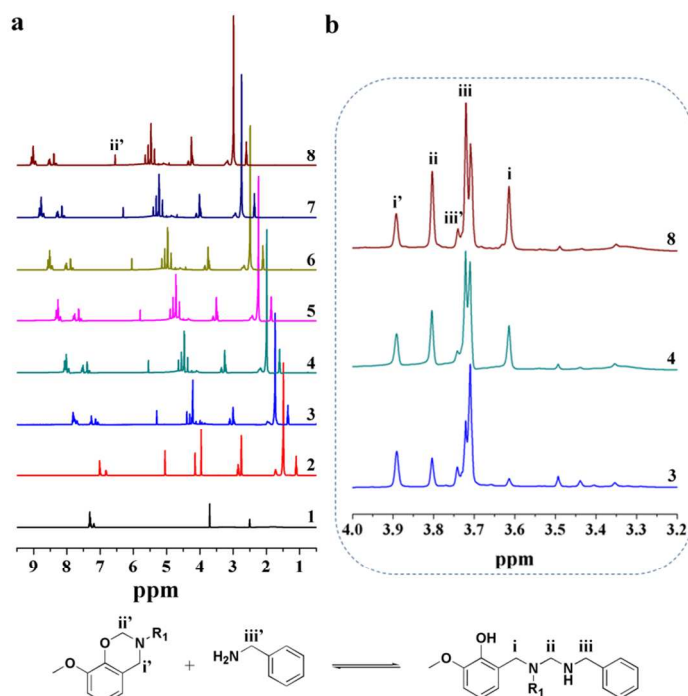


Fig. 7 NMR spectra of benzylamine (1), G-a (2) and the reactive mixture, G-a/benzylamine heated at 100 °C for (3) 0.5, (4) 10, (5) 20, (6) 30, (7) 60, and (8) 90 min.

number of new signals appeared in the region 4.0–3.5 ppm (i, ii, and iii), suggesting the formation of new methylene groups. These peaks reasonably support the scheme shown in Fig. 7: (1) they increased with reaction time; (2) the integrated areas are consistent with their parent compounds (e.g., the sum of the pair peaks of i and i' is nearly constant); (3) the assignment of the peaks to the methylene protons is logical. In addition, three peaks appeared in the range from $\delta = 3.5\text{--}3.3$ ppm upon heating, which remained small and almost unchanged during the whole reaction process. This phenomenon implies that these small peaks are caused by the by-products formed via side reactions, especially those involving the secondary amine formed during the ring-opening addition reaction. However, although a long heating process was examined, the characteristic peaks of the oxazine ring (at $\delta = 3.89$ and 4.80 ppm) were still observed in the NMR spectrum, which means that a considerable amount of G-a were unreacted.

To examine the conversion of the reactants during the heating process, we used HPLC equipped with a C18 reversed-phase column to separate and measure the benzylamine quantity in the mixtures heated for different times, and the results are shown in Fig. 8. The reaction rate of benzylamine is very rapid in the early stage, but gradually slows down to zero as the reaction progresses. This kinetic relationship shows that the ring-opening addition reaction between benzoxazine and the amine is reversible. In fact, this deduction has surprised us because a reversible reaction with kinetic features like those found in Fig. 8 (about 40 % benzylamine residue) cannot make any cured thermosetting resins.

The doubt whether or not free reactants exist in the cured resins leads us to carry out further investigations. We compared the FTIR spectra of two types of the cured BA-a/amine resins

(Fig.SI 2 and 3), one was heated at higher temperature to complete the curing reaction, and the other heated at 100 °C for 1.0 h to simulate the reaction that occurred in the NMR samples. As a result, the characteristic peaks attributed to the primary amine group were found only in the spectra of the products cured by arylamine (A1 and A5). We next extracted the completely cured resins (BA-a cured by the five commercial amines at 120 and 150 °C for 2 h, successively) with methanol in a Soxhlet extractor and analysed the extracting solution using a sensitive GC-MS method (with a minimum detectable quantity of <150 ng/mL), and no amines were detected. However, when the amine was changed to 2,4,6-Trimethylaniline (TMA) and 2,4,6-Trichloroaniline(TCA), 27 % and 35 % residue of the amine were detected, respectively (Fig.SI 4).

When the reactive mixtures of G-a/benzylamine were heated in their deuterated DMSO solution at higher temperatures, as shown in Fig. 9, more peaks appeared in the NMR spectra, indicating that a lot of additional methylene groups were formed. Based on the previous report³², the NMR peaks in the

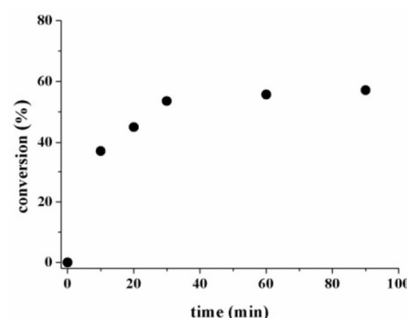


Fig. 8 The conversion of benzylamine in the reactive mixture, G-a/benzylamine heated at 100 °C. (benzylamine was detected by a HPLC method)


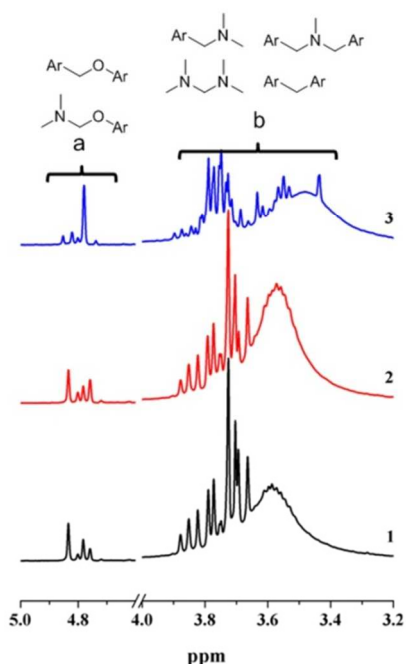


Fig. 9 NMR spectra of the reactive mixture, G-a/benzylamine heated at 150 °C for (1) 0.5 h and (2) 1 h, and (3) heated at 180 °C for 2 h.

range of $\delta = 4.9\text{--}4.7$ ppm were attributed to various $\text{Ar-OCH}_2\text{-}$ structures, and peaks in the range of $\delta = 3.9\text{--}3.4$ ppm were assigned to a wide variety of $\text{Ar-CH}_2\text{-N-}$, $\text{Ar-CH}_2\text{-Ar-}$, and $\text{N-CH}_2\text{-N-}$ structures. In short, these results suggest that following the reversible reaction between benzoxazine and the amine, complex reaction mechanisms will dominate the curing process at elevated temperatures.

3.4. The proposed reaction mechanism.

The cationic ring-opening polymerization mechanism proposed in Scheme 1a has been widely accepted by most researchers. A

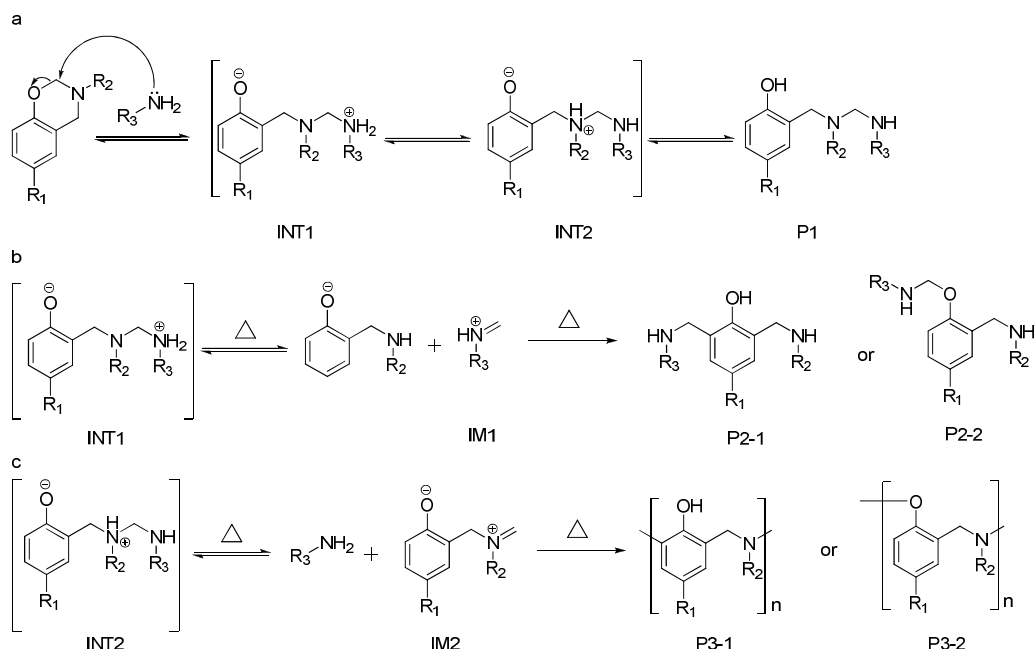

Scheme 3 Possible mechanisms of the reactions between amine and benzoxazine.

recent report has demonstrated a competitive pathway through phenoxy structures that finally convert to the phenolic polymers upon heating up to 160 °C³⁵. Soon afterward, some special compounds such as phenolic compounds, thiols, and chitosan ammonium, were used to react with benzoxazines^{42, 46, 49, 53, 59, 60} and a new mechanism, described as a ring-opening addition reaction mechanism (Scheme 1b) has been proposed⁴⁶. However, these mechanisms are not applicable for the experimental results we have described above. For example, most amines have a $\text{pK}_a > 30$ (in comparison to thiols with a pK_a 10–11 and ammonium ion pK_a 4–11), meaning that fewer protons can separate to form the anionic conjugate base (RNH_2^-). Another contradiction was reflected when comparing the reactivity of BA-a towards the five amines: an electron-withdrawing group like sulfone should theoretically stabilize the anionic conjugate base (RNH_2^-) and increase its reactivity towards BA-a, but we obtained the opposite finding in our experimental results.

Here we propose a detailed mechanism outlined in Scheme 3, in which three possible path ways dominate the curing process for the benzoxazine/amine mixtures at different stages. In the first reaction, the methylene group (at C8) between the nitrogen and oxygen is the most vulnerable position for nucleophilic attack of the amine both in terms of its partial charge and ring strain. As shown in Scheme 3a, a typical nucleophilic substitution reaction results in a zwitter ionic intermediate (INT1), which further produces another intermediate (INT2) and the product compound (P1) by proton transfer. In theory, the reactivity of the amine for this reaction is determined by its basicity. This conclusion is in good agreement with the small DSC peaks (at <120 °C) shown in Fig. 2, which were only observed with the alkylamine mixtures (in contrast with the arylamines, the DSC peaks are very small or undetectable).

Furthermore, the NMR data (Fig. 7) and the HPLC results (Fig. 8) further demonstrated that the first reaction is reversible. The two intermediates are thermally unstable and decompose upon heating at an elevated temperature (Scheme 3b and 3c), releasing the iminium ions IM1 and IM2 that are very reactive with aromatic rings and phenolic hydroxyl groups, and so should go on and produce P2 and P3 products through electrophilic substitution reactions (Scheme 3b and 3c). The two intermediates, INT1 and INT2, are a competitive pair in the first reaction. Their competitive advantage, which depends on which quaternary amine is favourable, determines the dominant pathway in the curing process and the dominant structures (P2 or P3) in the cured resin. In the cures of BA-a, P2 should be the main structure in the cured resin because the quaternary alkylamines (pKa 10–11.5) are more stable than that of the aromatic amines (pKa 4–6). In the DSC profiles of the alkylamine mixtures, the second reaction should be responsible for the peaks at 120–170 °C, as the order of the *Eap* values calculated from the peaks agree with the basicity for the amines.

On the other hand, when the aromatic amines (A1 and A5) were used to cure BA-a, the intermediate of INT2 will take little advantage over INT1. These results in the formation of the P3 structures and a few free amino groups will remain in the cured resin. This inference has been supported by the FTIR spectra (Fig.SI 2 and 3) obtained from the resin samples cured at 100 °C or at 120 and 150 °C for 2 h, as the primary amine groups were detected only from the arylamine (A1 and A5) cured resins. Because aromatic protons in the aromatic amines also react with the iminium ions (IM1 and IM2), aromatic amines can be cross-linked without the amino reactions. When a benzoxazine was cured with 2,4,6-tri-substituted amines (TMA and TCA), more amine residues were detected in the cured resins (Fig.SI 4). Since the residues of TCA were more than that of TMA, the results shown in Fig.SI 4 also support the competitive relevance between Scheme 3b and 3c. The interpretation is also applicable to the DMA test of amine A5, which largely decreased the storage modulus and the crosslinking density than bulk BF-a (Table SI 3).

With the above mechanism in mind, not only the resin's structure but also the curing reaction rate can be improved by choosing appropriate amine pairs, one used to synthesise the benzoxazine monomer and other used to cure the benzoxazine through a ring-opening addition reaction.

4. Conclusions

In summary, we have demonstrated the excellent nature of the ring-opening addition reaction of benzoxazine with an amine for the preparation of high performance thermosetting polymers. In contrast with the ring-opening polymerization of bulk BA-a, the addition of an amine not only achieved a much faster polymerization at mild temperatures (such as 120 °C or 150 °C), but also directly affected the characteristics of the amine thermally-cured benzoxazine resin. This fact was experimentally verified using five commercially available amines: m-phenylenediamine, m-xylylenediamine, isophorone diamine, trimethylhexamethylenediamine, and 4, 4'-diaminodiphenyl sulfone as the hardeners of BA-a monomer. The *Eap* values calculated from the dynamic DSC scans of the BA-a/amine

curing system revealed an expectable order of: arylamine > alicyclic amine > alkylamine, which is in good agreement with the basicity of the amines tested. Analysis of the FTIR and NMR spectra, and HPLC results further suggest that the curing reaction mechanism between the amine and benzoxazine involves: (1) a reversible reaction involving nucleophilic attack of the amine towards the benzoxazine to give zwitter ionic products with both phenolate and aminomethanaminium structures; (2) by heating at elevated temperature, the aminomethanaminium moiety decomposes to an iminium ion, and proceeds to take part in an electrophilic substitution reaction with the aromatic ring to form a stable aminomethylphenol structure. By addition of a suitable amine to the benzoxazine monomer, flexibility in the molecular design could be achieved to give the desired structures and the processability can be improved in terms of shorter curing time and lower curing temperature.

Acknowledgements

This work was financially supported by the Natural Science Foundation of Zhejiang Province (LY12E03007), the Scientific Research Foundation for the Returned Overseas Chinese Scholars, the State Education Ministry (1101603-C).

Notes and references

- ^aKey Laboratory of Advanced Textile Materials and Manufacturing Technology, Ministry of Education, College of Materials and Textile, Zhejiang Sci-Tech University, Xiasha Higher Education Zone, Hangzhou 310018, P.R. China. Tel&Fax: +86-571-8684-3785; E-mail: liuxd2007@gmail.com.
- ^bMolecular Engineering Institute, Kinki University, Kayanomori, Iizuka, 820-8555, Japan.
- † Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/b000000x/
- ‡ Footnotes should appear here. These might include comments relevant to but not central to the matter under discussion, limited experimental and spectral data, and crystallographic data.
1. X. Ning and H. Ishida, *J. Polym. Sci., Part A: Polym. Chem.*, 1994, **32**, 1121.
2. N. N. Ghosh, B. Kiskan and Y. Yagci, *Prog. Polym. Sci.*, 2007, **32**, 1344.
3. B. Kiskan, N. N. Ghosh and Y. Yagci, *Polym. Int.*, 2011, **60**, 167.
4. J. C. Ronda, G. Lligadas, M. Galia and V. Cadiz, *React. Funct. Polym.*, 2013, **73**, 381.
5. T. Endo and A. Sudo, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47**, 4847.
6. Y. Yagci, B. Kiskan and N. N. Ghosh, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47**, 5565.
7. A. D. Baranek, L. L. Kendrick, J. Narayanan, G. E. Tyson, S. Wand and D. L. Patton, *Polym. Chem.*, 2012, **3**, 2892.
8. K. D. Demir, B. Kiskan, B. Aydogan and Y. Yagci, *React. Funct. Polym.*, 2013, **73**, 346.
9. B. Kiskan, B. Koz and Y. Yagci, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47**, 6955.
10. R. Kudoh, A. Sudo and T. Endo, *Macromolecules*, 2010, **43**, 1185.
11. A. Chernykh, T. Agag and H. Ishida, *Macromolecules*, 2009, **42**, 5121.
12. K. D. Demir, B. Kiskan and Y. Yagci, *Macromolecules*, 2011, **44**, 1801.
13. H. Oie, A. Sudo and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 5357.
14. S. F. Li and T. Zou, *J. Appl. Polym. Sci.*, 2012, **123**, 922.

15. Y. Cheng, L. Kong, Z. Ren and T. Qi, *High Perform. Polym.*, 2013, **25**, 980.
16. Y. Cheng, J. Yang, Y. Jin, D. Deng and F. Xiao, *Macromolecules*, 2012, **45**, 4085.
17. Y. Cheng, T. Qi, Y. Jin, D. Deng and F. Xiao, *Polymer*, 2013, **54**, 143.
18. H. C. Chang, H. T. Lin and C. H. Lin, *Polym. Chem.*, 2012, **3**, 970.
19. I. Hamerton, L. T. McNamara, B. J. Howlin, P. A. Smith, P. Cross and S. Ward, *Macromolecules*, 2014, **47**, 1935.
20. I. Hamerton, L. T. McNamara, B. J. Howlin, P. A. Smith, P. Cross and S. Ward, *Macromolecules*, 2013, **46**, 5117.
21. I. Hamerton, L. T. McNamara, B. J. Howlin, P. A. Smith, P. Cross and S. Ward, *Macromolecules*, 2014, **47**, 1946.
22. B. Hanbeyoglu, B. Kiskan and Y. Yagci, *Macromolecules*, 2013, **46**, 8434.
23. O. S. Taskin, B. Kiskan and Y. Yagci, *Macromolecules*, 2013, **46**, 8773.
24. M. W. Wang, C. H. Lin and T. Y. Juang, *Macromolecules*, 2013, **46**, 8853.
25. K. D. Demir, B. Kiskan, S. S. Lathe, A. L. Demirel and Y. Yagci, *Polym. Chem.*, 2013, **4**, 2106.
26. S.C. Lin, C.S. Wu, J. M. Yeh and Y. L. Liu, *Polym. Chem.*, 2014, **5**, 4235.
27. C. Zhang, Y. Zhang, Q. Zhou, H. Ling and Y. Gu, *J. Polym. Eng.*, 2014, **34**, 561.
28. Y. S. Ye, Y. J. Huang, F. C. Chang, Z. G. Xue and X. L. Xie, *Polym. Chem.*, 2014, **5**, 2863.
29. A. Badshah, M. R. Kessler, Z. Heng, J. H. Zaidi, S. Hameed and A. Hasan, *Polym. Chem.*, 2013, **4**, 3617.
30. N. Ramdani, J. Wang, X. Y. He, T. T. Feng, X. D. Xu, W. B. Liu and X. S. Zheng, *Mater. Des.*, 2014, **61**, 1.
31. J. Wang, X. Y. He, J. T. Liu, W. B. Liu and L. Yang, *Macromol. Chem. Phys.*, 2013, **214**, 617.
32. H. Wang, J. Wang, X. Y. He, T. T. Feng, N. Ramdani, M. J. Luan, W. B. Liu and X. D. Xu, *RSC Adv.*, 2014, **4**, 64798.
33. M. Baqar, T. Agag, R. Huang, J. Maia, S. Qutubuddin and H. Ishida, *Macromolecules*, 2012, **45**, 8119.
34. P. Chutayothin and H. Ishida, *Macromolecules*, 2010, **43**, 4562.
35. C. Liu, D. Shen, R. M. Sebastián, J. Marquet and R. Schonfeld, *Macromolecules*, 2011, **44**, 4616.
36. J. Dunkers and H. Ishida, *J. Polym. Sci., Part A: Polym. Chem.*, 1999, **37**, 1913.
37. R. Andreu, J. Reina and J. Ronda, *J. Polym. Sci., Part A: Polym. Chem.*, 2008, **46**, 6091.
38. A. Sudo, S. Hirayama and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 479.
39. A. Sudo, A. Mori and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2011, **49**, 2183.
40. W. J. Burke, J. L. Bishop, E. L. M. Glennie and W. N. Bauer, *The Journal of Organic Chemistry*, 1965, **30**, 3423.
41. H. Oie, A. Mori, A. Sudo and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2012, **50**, 4756.
42. H. Oie, A. Mori, A. Sudo and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2013, **51**, 3867.
43. G. R. Goward, D. Sebastiani, I. Schnell, H. W. Spiess, H. D. Kim and H. Ishida, *J. Am. Chem. Soc.*, 2003, **125**, 5792.
44. A. Arnebold, O. Schorsch, J. Stelten and A. Hartwig, *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 1693.
45. A. Musa, B. Kiskan and Y. Yagci, *Polymer*, 2014, **55**, 5550.
46. A. W. Kawaguchi, A. Sudo and E. Takeshi, *ACS Macro Lett.*, 2013, **2**, 1.
47. Z. Beyazkilic, M. U. Kahveci, B. Aydogan, B. Kiskan and Y. Yagci, *J. Polym. Sci., Part A: Polym. Chem.*, 2012, **50**, 4029.
48. J. Narayanan, M. J. Jungman and D. L. Patton, *React. Funct. Polym.*, 2012, **72**, 799.
49. J. Bai, Z. Shi, J. Yin and M. Tian, *Macromolecules*, 2014, **47**, 2964.
50. S. K. Kim, S. W. Choi, W. S. Jeon, J. O. Park, T. Ko, H. Chang and J. C. Lee, *Macromolecules*, 2012, **45**, 1438.
51. K. Zhang, R. Cai, Q. Zhuang, X. Liu, G. Yang and Z. Han, *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 1514.
52. K. Zhang, R. Cai, Q. Zhuang, X. Liu, G. Yang and Z. Han, *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 1514.
53. A. A. Alhwaige, T. Agag, H. Ishida and S. Qutubuddin, *Biomacromolecules*, 2013, **14**, 1806.
54. H. Ishida, in *Handbook of benzoxazine resins*, eds. H. Ishida and T. Agag, Elsevier, Amsterdam, 2011, pp. 3.
55. H. E. Kissinger, *Anal. Chem.*, 1957, **29**, 1702.
56. R. Rogers and E. Morris Jr, *Anal. Chem.*, 1966, **38**, 412.
57. C. F. Wang, C. H. Zhao, J. Q. Sun, S. Q. Huang, X. D. Liu and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2013, **51**, 2016.
58. C. F. Wang, J. Q. Sun, X. D. Liu, A. Sudo and T. Endo, *Green Chem.*, 2012, **14**, 2799.
59. A. W. Kawaguchi, A. Sudo and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 1448.
60. A. W. Kawaguchi, A. Sudo and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 2523.

