

# Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

FULL PAPER

www.rsc.org/xxxxxx

## Structural, textural and acid-base properties of carbonates-containing hydroxyapatites†

Lishil Silvester<sup>a,b</sup>, Jean-François Lamonier<sup>a,b</sup>, Rose-Noëlle Vannier<sup>a,b,c</sup>, Carole Lamonier<sup>a,b</sup>, Mickaël Capron<sup>a,b</sup>, Anne-Sophie Mamede<sup>a,b,c</sup>, Frédérique Pourpoint<sup>a,b,c</sup>, Antonella Gervasini<sup>d</sup> and Franck Dumeignil<sup>a,b,e\*</sup>

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

Carbonates-containing hydroxyapatites with different Ca/P ratios and optionally containing Na<sup>+</sup> cations were successfully synthesized using a precipitation method. The solids were extensively characterized by XRD, LEIS, XPS, IR, TGA and NMR. Further, their acid-base properties were determined by NH<sub>3</sub>-TPD, PEA-XPS, CO<sub>2</sub>-TPD and by pulsed liquid chromatography using benzoic acid as a probe. The so-obtained structural, textural and acid-base properties could be finely correlated to give a clear picture of the system. Acid properties of hydroxyapatites were attributed to Ca<sup>2+</sup>, surface HPO<sub>4</sub><sup>2-</sup> and OH<sup>-</sup> vacancies and the basic properties were attributed to PO<sub>4</sub><sup>3-</sup>, OH<sup>-</sup> and CaO species. The fine-tuning of the amount, of the nature and the strength of acid-base properties derived by varying the carbonate content in hydroxyapatites can find applications in catalysis, which was illustrated by *isopropanol* reactivity.

### 1 Introduction

Natural hydroxyapatite (HAP), with the formula Ca<sub>10</sub>(PO<sub>4</sub>)<sub>6</sub>(OH)<sub>2</sub>, is the most stable calcium phosphate salt, and is the main inorganic constituent of biological hard tissues in animal organisms. It can be synthesized at various temperatures, typically below 373K, and at a pH between 4 and 12. It drives a considerable interest in medical applications, in chromatography, as a fertilizer, in the pharmaceutical industry, and in the field of catalysis.<sup>1,2,3</sup> HAP contains both acid and basic sites in a single crystal lattice<sup>4,5</sup>, and can thus be applied to reactions requiring bifunctional solid catalysts containing both antagonist functionalities, such as the Guerbet reaction<sup>6</sup>, the Michael addition, the Knoevenagel condensation<sup>7</sup>, the Claisen-Schmidt condensation or the Friedel-Crafts reaction.<sup>8</sup> The aforementioned native HAP authorizes large variations in compositions, and, as a general matter, the so-called 'HAPs' are highly non stoichiometric solids with the general formula 'Ca<sub>10-x</sub>(PO<sub>4</sub>)<sub>6-x</sub>(HPO<sub>4</sub>)<sub>x</sub>(OH)<sub>2-x</sub>', with 0 < x ≤ 1. This yields a family of compounds with very different properties, from more acidic solids in the case of deficient HAPs (x > 0) to solids more and more basic when approaching the stoichiometry of the native HAP (x = 0), this latter being, therefore, predominantly basic.<sup>2,9,10</sup> The Ca/P ratio is commonly used as an index of their non-stoichiometry (the stoichiometric ratio being 1.67) and of their acid-base behaviour. It is well known that HAPs act as solid acid catalysts when Ca/P ≈ 1.50, and develop both the acid and the basic characters when the Ca/P ratio is between 1.50 and 1.67.<sup>11-</sup>

In addition to varying the Ca/P ratio, the surface acid-base properties of the HAPs can also be tuned by replacing Ca<sup>2+</sup> ions by vacancies or cations such as Sr<sup>2+</sup>, Mg<sup>2+</sup>, Na<sup>+</sup>, K<sup>+</sup>, etc. Substitution of OH<sup>-</sup> anions by vacancies, F<sup>-</sup>, Cl<sup>-</sup>, CO<sub>3</sub><sup>2-</sup> and/or PO<sub>4</sub><sup>3-</sup> anions by CO<sub>3</sub><sup>2-</sup>, HPO<sub>4</sub><sup>2-</sup>, VO<sub>4</sub><sup>3-</sup>, etc..., are other possibilities. The structure of HAP comprises three-dimensional networks of hexagonally packed tetrahedral PO<sub>4</sub><sup>3-</sup> ions. These ions make a first channel around Ca<sup>2+</sup> ions [Ca (I)] with a diameter of 2.5 Å.<sup>16,17</sup> A second channel with a diameter of 3.5 Å, bordered by triangular Ca<sup>2+</sup> ions [Ca (II)], hosts the OH<sup>-</sup> species along the *c*-axis.<sup>18</sup> The structure is flexible to both cationic and anionic substitutions, which yields the aforementioned possibility of modulating the number of acid-base sites in the HAP crystal. Cations can substitute either Ca (I) or Ca (II) ions or both ions simultaneously, and anions can replace either OH<sup>-</sup> or PO<sub>4</sub><sup>3-</sup> ions or both.<sup>11</sup> The general formula for carboapatites, in which CO<sub>3</sub><sup>2-</sup> ions can be located in two different positions, is Ca<sub>10</sub>[(PO<sub>4</sub>)<sub>6-x-y</sub>(HPO<sub>4</sub>)<sub>x</sub>(CO<sub>3</sub>)<sub>y</sub>][(OH)<sub>2-(x+y)</sub>(CO<sub>3</sub>)<sub>x+y</sub>], considering that the charge loss due to the PO<sub>4</sub><sup>3-</sup> substitution (B-type substitution) is counterbalanced by addition of CO<sub>3</sub><sup>2-</sup> in the OH<sup>-</sup> sites (A-sites).<sup>19</sup> If some defects arise due to the formation of vacancies or related substitution of Ca by Na, charge will be compensated by less carbonates in A-sites.

Different substitutions not only result in a variation in the balance between the acidic and the basic nature of the solid HAPs surface, but may also change their morphology. Some studies have reported a correlation between the exposure to the surface of HAPs specific components such as Ca<sup>2+</sup> and PO<sub>4</sub><sup>3-</sup> groups, with

the type of crystallite growth.<sup>3,19-21</sup> However, their conclusions are contradictory and a deeper understanding effort is then required. In the present work, using X-ray diffraction (XRD) & Rietveld refinement as well as TGA, we precisely determined the crystallite nature and the global formula of HAPs prepared with varying the Ca/P ratio (or the carbonate content). The types of carbonate substitution were determined by IR spectroscopy. The presence of orthophosphate and of  $\text{HPO}_4^{2-}$  groups in the HAPs was qualitatively evaluated with the help of CP MAS-NMR and 2D-HETCOR NMR spectroscopy. Further, X-Ray Photoelectron Spectroscopy (XPS) complemented by Low Energy Ion Scattering (LEIS) was used to precisely determine the surface composition of the solids, in order to enable identification of any potential correlation with the crystallites growth/morphology. The total numbers of acid and of basic sites in the HAPs was determined by Thermo-Programmed Desorption of  $\text{NH}_3$  (TPD- $\text{NH}_3$ ) and of  $\text{CO}_2$  (TPD- $\text{CO}_2$ ), respectively. We also determined the distribution of the nature of the surface acid sites (Lewis & Brønsted) by XPS after adsorption of 2-phenylethylamine (PEA) used as a probe molecule.<sup>22</sup> Pulse liquid chromatographic technique<sup>23</sup> using benzoic acid as a probe molecule was further used to determine the amount and strength of basic sites in the hydroxyapatites directly in the liquid phase. The surface acid-base reactivity was further evaluated using isopropanol reactivity as a test model reaction.

## 2 Experimental

### 2.1 Materials

Reagent grade chemicals such as calcium nitrate tetrahydrate,  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  ( $\geq 99.0\%$ ), ammonium dihydrogen phosphate,  $(\text{NH}_4)_2\text{H}_2\text{PO}_4$  ( $\geq 98.0\%$ ), sodium nitrate,  $\text{NaNO}_3$  (99.0%), and sodium carbonate,  $\text{Na}_2\text{CO}_3$  ( $\geq 99.0\%$ ) (Sigma Aldrich) were used as starting materials.

### 2.2 Samples preparation

All the solids were synthesized by a precipitation method reported elsewhere.<sup>24</sup> Deficient and stoichiometric HAPs were prepared by fixing the Ca/P molar ratios of the synthesis solutions at 0.9 and 1.67, respectively. Two carbonated apatites with and without sodium were synthesized by moderately increasing the (Ca + Na)/P ratio of the solutions from the stoichiometric value of 1.67 to 2, with a Ca/Na molar ratio of 5.7 for the Na-containing solid. Finally, two carbonate-rich apatites with and without sodium were synthesized by increasing the (Ca + Na)/P ratio of the solutions from the stoichiometric value of 1.67 to 5.5 with a Ca/Na molar ratio of 5 for the Na-containing solid. The detailed preparation procedures of these samples are given below.

A stoichiometric hydroxyapatite (Hap) was synthesized by adding dropwise 300 mL of an aqueous solution containing 0.167 mol of  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  to 1000 mL of a 0.1 mol of  $(\text{NH}_4)_2\text{H}_2\text{PO}_4$  solution placed under stirring at 353 K. The pH during synthesis was maintained at 10 by properly adding a 25%  $\text{NH}_4\text{OH}$  solution. The formed precipitate was slowly filtered, washed with hot water, and dried at 353 K before being calcined for 4 h under oxygen at 673 K ( $2 \text{ K} \cdot \text{min}^{-1}$ ). Lowering the calcium quantity in the solution from 0.167 mol to 0.09 mol resulted in the formation of a calcium deficient hydroxyapatite (HapD).

For carbonated hydroxyapatite with  $\text{Ca/P} > 1.67$ ,  $\text{CO}_2$  was

naturally introduced from the atmosphere as  $\text{CO}_3^{2-}$  anions, which were incorporated to compensate the charge due to excess calcium cations in the apatite solids. In this respect, the carbonated apatite (Hap- $\text{CO}_3$ ) was prepared by using a Ca/P molar ratio of 2 in the precursor solutions instead of the stoichiometric value of 1.67. The same procedure was used to synthesize a sodium-containing carbonate apatite (HapNa- $\text{CO}_3$ ) prepared with a Ca/Na molar ratio of 5.7, keeping a (Ca + Na)/P molar ratio of 2.

A carbonate-rich hydroxyapatite was synthesized by adding dropwise an aqueous solution of 0.1 mol of  $(\text{NH}_4)_2\text{H}_2\text{PO}_4$  (0.1 M) to a 300 mL solution containing 0.55 mol of calcium nitrate placed under stirring at 353 K. The higher Ca/P molar ratio of 5.5 compared to the stoichiometric value of 1.67 allowed us to introduce a higher quantity of carbonate ions in the synthesized hydroxyapatite. The corresponding solid was denoted as HapE- $\text{CO}_3$ , which is thus a sodium-free carbonate-rich apatite. Even more carbonate ions and sodium ions were also introduced in a last sample, using sodium carbonate (5.83 g) dissolved in 1000 mL of an ammonium hydrogen phosphate solution (0.1 M). The Ca/Na molar ratio of the solution was fixed at 5. In that case, the resulting solid was a sodium-containing carbonate-rich apatite denoted as HapE-Na- $\text{CO}_3$ .

### 2.3 Characterization methods

The chemical composition of the samples was determined at the 'Service Central d'Analyses du CNRS' (Vernaison, France) using Inductively Coupled Plasma Mass Spectrometry ICP-MS. Before ICP-MS chemical analyses, the samples were dissolved in acidic media.

The specific surface areas were determined using a conventional multi point BET Nitrogen adsorption method using a Micrometrics Tristar II apparatus. Prior to nitrogen adsorption, the samples were outgassed for 4 h at 423 K under nitrogen flow.

Thermo gravimetric analysis (TGA) was performed using a Thermal Analysis instrument (TG92 Setaram) connected with a mass spectrometer (Omnistar), on 15 mg of sample. The weight loss was recorded under synthetic air, at a heating rate of  $10 \text{ K} \cdot \text{min}^{-1}$  from room temperature to 1273 K.

Routine powder X-Ray diffractograms were recorded at room temperature (RT) using a Bruker AXS D8 Advance diffractometer working in a Bragg-Brentano geometry and equipped with a LynxEye Super Speed detector. Data were collected using the  $\text{CuK}\alpha_{1,2}$  line in the  $10\text{-}90^\circ 2\theta$  range with a  $0.02^\circ 2\theta$  step. The Fullprof Suite program was used for Rietveld refinement.<sup>25</sup> The Thompson-Cox-Hastings pseudo-Voigt function was chosen for describing the peak profiles.  $\text{LaB}_6$  was used as a standard to derive the instrument resolution.<sup>26</sup> Here, an anisotropic size-broadening model based on linear combination of spherical harmonics was used to simulate the size broadening, and 6 additional parameters were refined. From this refinement, individual size was derived for each crystallographic plane.

Temperature-programmed XRD was also carried out on a Bruker AXS D8 advanced apparatus equipped with an Anton Paar HTK1200N high temperature chamber, and connected to a VANTEC fast linear detector, which enables short acquisition time. Each sample was deposited on a Pt sheet. The experiments were performed by increasing the temperature from 323 K to 1273 K, while acquiring a diffractogram every 25 K. The data

acquisition parameters correspond to an angular range of  $10^{\circ}$ - $70^{\circ}$  with a step of  $0.015^{\circ}$  and an acquisition time of 0.22 s per step.

The morphology of the catalysts was observed using Scanning Electron Microscopy images recorded on a Hitachi S-4700 apparatus with a 50 k magnification.

Transmission infrared (IR) spectra were recorded from  $400\text{ cm}^{-1}$  to  $4000\text{ cm}^{-1}$  at room temperature under vacuum in a Nicolet 460 Fourier transform infrared spectrometer. The samples were prepared by intimately mixing 1 mg of powdered sample with 150 mg of dried KBr.

All the 1D and 2D MAS-NMR (CP HETCOR) spectra were recorded at room temperature using a Bruker Advance spectrometer working at a  $^1\text{H}$  Larmor frequency of 400 MHz (9.4 T). The resonance frequency of  $^{31}\text{P}$  was then 161.9 MHz. A Bruker 4 mm CP MAS probe was used to perform all the experiments at a spinning speed of 10 kHz. The chemical shifts were determined using tetramethylsilane (TMS) (0 ppm) and  $\text{H}_3\text{PO}_4$  ( $\delta = 0$  ppm) as reference compounds, for  $^1\text{H}$  and  $^{31}\text{P}$  spectra, respectively.

The surface Ca/P ratio and the  $\text{CO}_3^{2-}$  content of the HAPs were determined from the areas of the Ca 2p, P 2p and C 1s photopeaks recorded using XPS on a Kratos Axis Ultra<sup>DL</sup> spectrometer. Photoelectrons generated by a monochromatic Al-K $\alpha$  X-ray radiation source operating at 150 W (15 kV, 10 mA) having initial kinetic energies of up to 1486.7 eV ensured an average depth for electron escape of  $\sim 1$ -10 nm. High-resolution scans were acquired with 40 eV pass energy and 300 ms dwell times. All the resulting binding energy values were corrected using the C 1s peak (C-C) fixed at 285 eV as a reference.

LEIS spectra were recorded using a Qtac<sup>100</sup> spectrometer (ION TOF GmbH). The spectra were obtained using a 3 keV  $^4\text{He}^+$  beam. Assuming a sputter yield of 0.1 atoms per He-ion under a 4 nA target current, the total dose density was less than  $3.0 \times 10^{13}$  atoms per  $\text{cm}^2$ .

The density of acid sites in the samples was determined by TPD- $\text{NH}_3$  using a Micrometrics apparatus equipped with a mass spectrometer. 150 mg of sample were purged for 30 min in a He flow of  $40\text{ mL}\cdot\text{min}^{-1}$  at 673 K before being naturally cooled to room temperature. The sample was then contacted with a 10%  $\text{NH}_3/\text{He}$  atmosphere during 30 min in a  $30\text{ mL}\cdot\text{min}^{-1}$  flow before being further purged for 2 h at room temperature under a  $50\text{ mL}\cdot\text{min}^{-1}$  He flow. After purging, the temperature was raised at a rate of  $10\text{ K}\cdot\text{min}^{-1}$  to 873 K in a  $30\text{ mL}\cdot\text{min}^{-1}$  He flow. The quantity of desorbed  $\text{NH}_3$  was determined by mass spectrometry using the peak with  $M/Z = 15$ .

The density in basic sites was similarly evaluated using TPD- $\text{CO}_2$  with 5%  $\text{CO}_2/\text{He}$  on the same micrometrics apparatus under the same conditions as those employed for TPD- $\text{NH}_3$ . The quantity of basic sites was determined by mass spectrometry using the peak located at  $M/Z = 44$ .

The nature of the medium-strong acid sites was then determined by PEA-XPS analysis, using the adsorption of PEA as a probe molecule before XPS measurement.<sup>22</sup> Prior to the adsorption, the calcined samples were outgassed at 523 K for 4 h under Ar flow. The cleaned powder was then transferred to a glass cell connected with vacuum/gas lines, and liquid PEA (purity > 99%, purchased from Fluka) was introduced in the cell to cover up the powder during 2 h under an Ar flow. Then, the

excess of non-adsorbed PEA was removed by filtration using primary vacuum in the presence of an Ar flow. The sample was then directly transferred to the chamber of the spectrometer for analysis. PEA is a strong base that can be retained by weak, medium, and strong acid sites over solid surfaces. Note that XPS measurements of PEA provide information only on the strong and medium acid sites and not on the weakest sites, which cannot hold this probe under the ultra-high vacuum conditions of the analyses, this latter being desorbed under such harsh conditions.<sup>22</sup>


A pulsed liquid chromatographic technique<sup>23</sup> was further used for the determination, directly in a liquid phase, of the amount of the surface basic sites using benzoic acid adsorption. All the experiments were conducted using a liquid chromatography (HPLC) connected to a Waters model 510 pump, a Rheodyne 7725 injector and a Waters model 2487 UV detector coupled to a personal computer for the collection and data processing. The sample was placed in a sample holder, under the form of a small stainless steel tube (*i.d.* = 2 mm, length = 12 cm) placed in replacement of the chromatographic column in the HPLC. Prior to analysis, the sample was placed at the centre of the sample holder tube, supported by silica wool and acid-washed sea sand (Fluka), which are totally inert towards the adsorption of the benzoic acid probe. For each experiment, a weighted amount of fresh sample was outgassed in a furnace for 16 h at 623 K under air flow ( $8\text{ mL}\cdot\text{min}^{-1}$ ), and then the cell was evacuated under vacuum before being filled with cyclohexane as an apolar-aprotic solvent. The linearity of the chromatographic response as a function of the benzoic acid concentration in cyclohexane was checked by injecting known concentrations of benzoic acid solutions. In each adsorption test, pulses consisting of 20  $\mu\text{L}$  benzoic acid solution of a known concentration of  $0.05\text{ mol}\cdot\text{L}^{-1}$  were passed through the sample at a constant cyclohexane flow rate ( $0.5\text{ mL}\cdot\text{min}^{-1}$ ). The unabsorbed amount of benzoic acid after each pulse was recorded until the sample saturation (total recovery of the benzoic acid in the injected pulse and completion of the first cycle). If a 1:1 adsorption stoichiometry is assumed in this cycle, the total number of basic sites corresponds to the total amount of benzoic acid adsorbed on the sample. In the second cycle, the sample was purged with cyclohexane ( $0.05\text{ mol}\cdot\text{L}^{-1}$ ) to remove the weakly adsorbed benzoic acid molecules on the solid surface. Finally, a third benzoic acid adsorption cycle similar to the first cycle was performed which determines the amount of benzoic acid molecules removed during the purge and therefore the weak basic sites. The amount of strong basic sites is thus calculated by the difference between the total amount of basic sites (titrated in the first cycle) and the amount of weak basic sites obtained in the third cycle.

Acid-base properties of all the solids were finally evaluated using a test catalytic reaction, namely the *isopropanol* conversion, which gives propylene (and also small amounts of *di-isopropylether*, which was detected over some samples), over acid sites and acetone over basic sites. The selectivity of the samples was compared at 20% iso-conversion of *isopropanol*, which was adjusted by properly setting the reaction temperature (typically between 548 K and 623 K). The reaction was carried out in a glass flow reactor working at atmospheric pressure. The solid was ground and sieved to a particle size in the 80-100  $\mu\text{m}$  range. This powdered and sieved material (100 mg) was then

mixed with an equal quantity of carborundum (120  $\mu\text{m}$ ) and used as a catalyst bed followed by another layer of 500 mg carborundum to ensure thermal homogeneity and smooth heat transfer inside the reactor. The reactant feed containing 2 mol% of isopropanol was obtained by bubbling He (25 mL.min<sup>-1</sup>) through liquid isopropanol placed in a saturator maintained at 283 K. The reaction products were analysed on-line using a gas chromatograph equipped with a HP-INNOWax column ( $l = 30$  m,  $i.d. = 0.25$  mm, film thickness = 0.50  $\mu\text{m}$ ) and a flame ionization detector.

### 3 Results and discussion

#### 3.1 Bulk composition of the solids

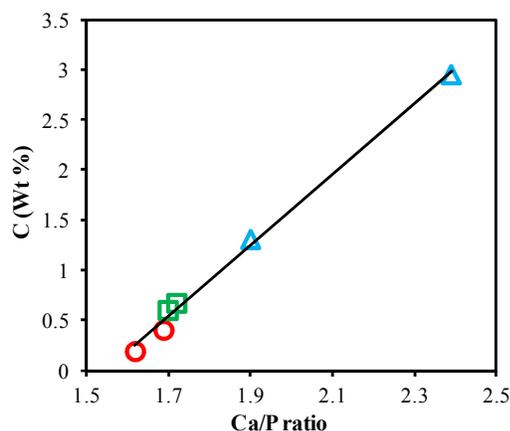

**Fig. 1** Carbon content as a function of the bulk Ca/P ratio of the solids (circles representing HapD and Hap, squares for carbonated apatites, namely Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub>, and triangles for carbonate-rich apatites, namely HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>).

It is known that the Ca/P atomic ratios obtained by chemical analysis of the final solids differ from those of the solutions used during their synthesis.<sup>27,28</sup> The Ca/P atomic ratios of all the prepared samples (Table 1) were indeed lower than the Ca/P molar ratios in the preparation solutions, except for the deficient and the stoichiometric apatites, namely HapD and Hap. Indeed, for HapD and Hap, the Ca/P atomic ratios in the solid were 1.62 and 1.69, respectively, compared with 0.9 and 1.67 fixed during their synthesis. The chemical compositions of the solids further show that an increase in the Ca/P ratio was accompanied with a linear increase in the carbon content (Figure 1), which can most probably be attributed to the introduction of carbon under the form of carbonate ions in the apatite structure, in substitution to phosphate ions (*vide supra*).

#### 3.2 Specific surface areas


The specific surface areas of all the calcined solids were larger than 100 m<sup>2</sup>.g<sup>-1</sup>, except for the carbonates-rich apatites, namely HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>, with 76 and 72 m<sup>2</sup>.g<sup>-1</sup>, respectively (Table 1). Hence, this underlines that this preparation method carried out in open atmosphere can provide apatites with high surface areas, which however decreased a little bit when introducing CO<sub>3</sub><sup>2-</sup> ions in the case of carbonate-rich solids.

**Table 1** Chemical composition and specific surface area of the prepared solids calcined at 673 K.

Type of solid	Name	(Ca + Na)/P molar ratio in solutions	Ca/P atomic ratio (ICP)	Ca (wt.%)	P (wt.%)	Na (wt.%)	C (wt.%)	Specific surface area (m <sup>2</sup> .g <sup>-1</sup> )
Deficient	HapD	0.9	1.62	37.06	17.69	-	0.18	124
Stoichiometric	Hap	1.67	1.69	38.45	17.54	-	0.40	114
Carbonated	Hap-CO <sub>3</sub>	2.0	1.70	38.10	17.29	-	0.59	107
Carbonated	HapNa-CO <sub>3</sub>	2.0	1.72	38.17	17.14	0.64	0.67	109
Carbonate-rich	HapE-CO <sub>3</sub>	5.5	1.90	37.03	15.04	-	1.30	76
Carbonate-rich	HapE-Na-CO <sub>3</sub>	6.6	2.39	39.47	12.75	< 0.3	2.95	72

#### 3.3 Structure of the solids

##### 3.3.1 Crystallographic structure

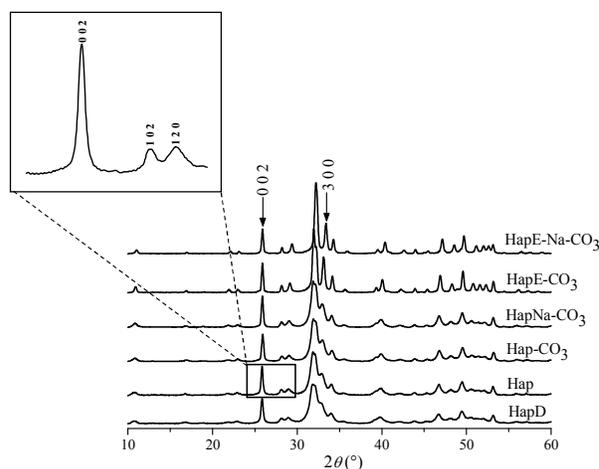

**Fig.2** XRD patterns of the calcined solids.

All the X-ray diffraction patterns suggested the exclusive presence of the crystalline hydroxyapatite phase (JCPDS 01-084-1998) with small differences in Bragg peak positions (Figure 2).<sup>29</sup>

A small shift of the (3 0 0) Bragg peak towards higher  $2\theta$  values associated to a better crystallinity was observed when the carbonate content increased from HapD ( $2\theta = 32.8^\circ$ ) to HapE-Na-CO<sub>3</sub> ( $2\theta = 33.4^\circ$ ).

The apatite structure was refined in the  $p6_3/m$  space group, using the structure model proposed by Hughes *et al.*<sup>29</sup> The atomic positions of all the atoms were refined. To take into account the thermal vibrations, an overall parameter was used for all the crystallographic sites. For all the samples, the XRD pattern

showed a thinner Full Width at Half Maximum (FWHM) for the (0 0 2) reflection compared to the FWHM of the other reflections (see insert in Figure 2 and Figure S1†), indicating the presence of anisotropic crystallites. Therefore, an anisotropic size-broadening model based on linear combination of spherical harmonics was used to simulate the size broadening<sup>30</sup>, taking into account the instrument resolution from a LaB<sub>6</sub> pattern. From this model, the crystallites shape was deduced. For Hap and HapE-Na-CO<sub>3</sub> taken as examples, a good agreement was obtained between the calculated and the experimental data in all the solids (Figure S2†). All the results are summarized in Table 2.

**Table 2** Cell Parameters, phosphorus occupancy and crystallite size determined using Rietveld refinement.

Solids	Cell Parameters		Phosphorus site occupancy (%)	(Ca + Na)/P [ICP]	Crystallite size (nm) corresponding to crystallographic plane		Length/ thickness ratio (0 0 1)/(1 0 0)
	<i>a</i> (Å)	<i>c</i> (Å)			(1 0 0)	(0 0 1)	
HapD	9.4210(6)	6.8853(4)	97.0(4)	1.72(5) [1.62]	7	22	3.2
Hap	9.4103(5)	6.8871(4)	94.6(4)	1.76(2) [1.69]	8	26	3.2
Hap-CO <sub>3</sub>	9.4142(5)	6.8876(4)	93.8(4)	1.77(2) [1.70]	9	30	3.3
HapNa-CO <sub>3</sub> *	9.4106(6)	6.8909(4)	93.8(4)	1.78(2) [1.77]	10	36	3.6
HapE-CO <sub>3</sub>	9.3742(5)	6.8891(4)	89.4(4)	1.87(2) [1.90]	23	55	2.4
HapE-Na-CO <sub>3</sub>	9.3111(8)	6.8982(6)	78.6(4)	2.12(2) [2.39]	23	41	1.8

\* Na occupancy was refined in the case of HapNa-CO<sub>3</sub> (see text).

N.B. Standard deviation for unit cell parameters, phosphorous occupancy and (Ca + Na)/P ratio are given in brackets by taking into account the Berar factor.<sup>31</sup>

As expected, a decrease in the *a* values with increasing the carbonate content from 9.4210(4) Å in HapD to 9.3112(2) Å in HapE-Na-CO<sub>3</sub> was observed except for Hap, which showed a lower *a* value compared to Hap-CO<sub>3</sub>. This observation is in good agreement with the partial substitution of phosphate groups by carbonate ions, as previously reported.<sup>32-34</sup> In contrast, an increase in the carbonate content led almost to no evolution of the *c* value, which corresponds to the stacking direction of the apatite structure. Only a slight increase in the *c* value was observed for the sodium-containing samples (HapNa-CO<sub>3</sub> & HapE-Na-CO<sub>3</sub>), as already reported for sodium-substituted apatites compared to pure Hap.<sup>33,35</sup>

While structure models have been proposed for carbonate-containing apatites<sup>33</sup>, because of the too low X-Ray scattering length of carbon atoms, it was not possible here to refine the carbonate positions. However, we could confirm the partial substitution of phosphate groups by refining the occupancy of phosphorous sites, thereby indirectly determining the occupancy of carbonates from the vacancies in the phosphorous sites. The phosphorous vacancies were then refined for all the compositions (Table 2). As expected, the refinements led to the lowest phosphorous occupancies of 89.4(4)% and 78.6(4)%, respectively in the carbonate-rich HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub> samples, compared to the other apatites. This reveals the presence of higher amounts of carbonates in the phosphorous sites of carbonate-rich apatites, which is in good agreement with the introduction of carbonates in the P sites (B-type apatite sites). It was not possible to refine the Na occupancy in the calcium site of HapE-Na-CO<sub>3</sub>, in good agreement with the low sodium amount

observed by ICP. In the case of HapNa-CO<sub>3</sub>, introduction of sodium in the Ca (I) site led to a small occupancy corresponding to 0.18(9) Na for 9.82 calcium atoms in the apatite, in rather good agreement with the sodium amount measured by ICP (0.28 wt.%). Moreover, introduction of Na in the Ca (II) sites led to a negative occupancy, indicating a preference of Na for the Ca (I) sites, and, therefore, in the refinement, sodium was introduced only in the Ca (I) sites. For the deficient apatite (HapD), refinement of calcium sites occupancies led to unrealistic values, which were higher than '1'. Therefore, the calcium occupancy was fixed to 1, and it was thus not possible to confirm the calcium deficiency only using X-ray diffraction. Moreover, for this composition, a phosphorous occupancy of 97.0(4)% was obtained, suggesting the presence of a small amount of carbonates in the B sites.

Figure S3† shows that the (Ca + Na)/P ratio refined from XRD data increased linearly with the same ratio determined by ICP. However, the XRD-deduced ratios exhibited a slight deviation from the so-to-speak ideal ICP ratio, especially for HapE-Na-CO<sub>3</sub> with higher Ca+Na/P ratio compared to the other apatites. In terms of phosphorous site occupancy, this makes a difference of 10% with 79% (ICP) to be compared to 69% (XRD). This deviation can be explained by the limited accuracy on the phosphorus occupancy from XRD data, since the overall parameter was used in refinement for all the crystallographic sites, and the thermal vibrations and occupancies in such refinement are strongly correlated.

### 3.3.2 Crystallites and grain shape

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

FULL PAPER

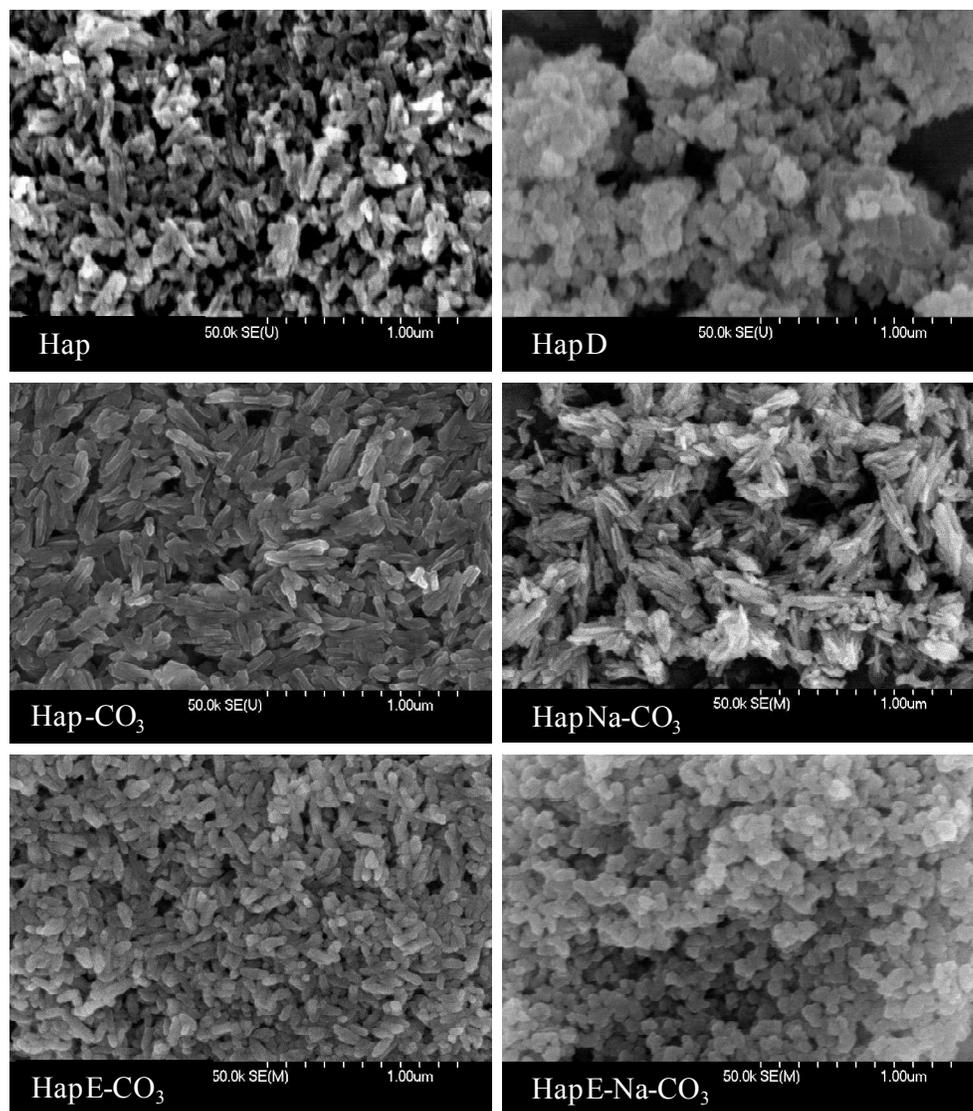


Fig.3 SEM images of calcined samples at 50.0 k magnification.

As aforementioned, an anisotropic size-broadening model was used to deduce the crystallites size. As shown in table 2, the crystallite size along the (1 0 0) and (0 0 1) planes, determined by Rietveld refinement, indicated that the crystal growth increased with an increase in the Ca/P ratio or carbonate content (Table 2), these parameters being correlated. The crystallite size was much higher for carbonate-rich HapE-CO<sub>3</sub> (23 nm & 55 nm) and HapE-Na-CO<sub>3</sub> (23 nm & 41 nm) when compared to stoichiometric Hap (8 nm & 26 nm) (Table 2). The length/thickness ratios of Hap and HapD were identical (3.2), and slightly higher for Hap-CO<sub>3</sub> (3.3) and HapNa-CO<sub>3</sub> (3.6), which contains just a few carbonates, suggesting similar elongated crystallite shapes. In contrast, a

15 lower length/thickness ratio was observed for the apatites richer in carbonates (2.4 & 1.8), thus indicating that the crystallites became more spherical for carbonate-rich apatites (Table 2).

To verify whether the crystallite shapes obtained by Rietveld refinement have an influence on the grain shape, Scanning Electron Microscopy pictures were taken. The anisotropy observed by XRD was then confirmed by SEM (Figure 3). Irregularly shaped agglomerates were observed for stoichiometric (Hap) and deficient apatites (HapD), while flat needle/rod-shaped clusters were observed for the carbonated apatites Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub>. The pictures also revealed capsule and spherically shaped grains for HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>, respectively. In

all the cases, the grain shapes were thus in good agreement with the crystallite shape determined by refinement from XRD diffractograms. However, using SEM, bigger particles with length in the order of 100  $\mu\text{m}$  were observed, indicating agglomerated poly-crystallite grains.

### 3.3.3 Amount and type of carbonates substitution

#### 3.3.3.1 Thermal stability and carbonate content

To check the thermal stability of the apatite solids, temperature-programmed XRD was carried out using 3 selected compositions, namely HapD (a deficient apatite), Hap-CO<sub>3</sub> (carbonated apatite very similar to Hap and HapNa-CO<sub>3</sub>), and HapE-Na-CO<sub>3</sub> (a carbonate-rich apatite, similar to HapE-CO<sub>3</sub>). The deficient apatite HapD was chosen, since it is supposed to decompose to stoichiometric apatite (Hap-like) and Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub>,<sup>27,36</sup> whereas all the other apatites with Ca/P ratio higher than 1.67 should decompose to stoichiometric apatite and CaO<sup>27</sup>. The so-obtained series of X-ray patterns are given in Figure S4†. As expected,

HapD decomposed to stoichiometric apatite and Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> with the appearance of two forms of Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub>, namely  $\alpha$ -Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> (JCPDS 01-070-0364) and *syn*-Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> (JCPDS 00-009-0169), at 973 K. Compared to normal stoichiometric apatites (Ca/P = 1.67), Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> formed from deficient HapD exhibits a smaller Ca/P ratio of 1.5 and the formation of Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> is thus an indirect proof of calcium deficiency in HapD. In contrast, for temperatures higher than 998 K, the formation of calcium oxide was observed for Hap-CO<sub>3</sub>, and the same transformation was noticed at around 898 K for HapE-Na-CO<sub>3</sub> for which, in addition, a slight modification of the X-ray pattern was noticed at 823 K. It was characterised by a decrease in intensity and an increase in the FWHM of the (0 0 2) Bragg peak, and by the appearance of an additional peak around  $2\theta = 29.5^\circ$ , which further disappeared at 923 K, maybe due to the reconstruction of the apatite structure (Figure S4†). Since only one additional Bragg peak was observed, it was not possible to go further in the understanding of this modification.

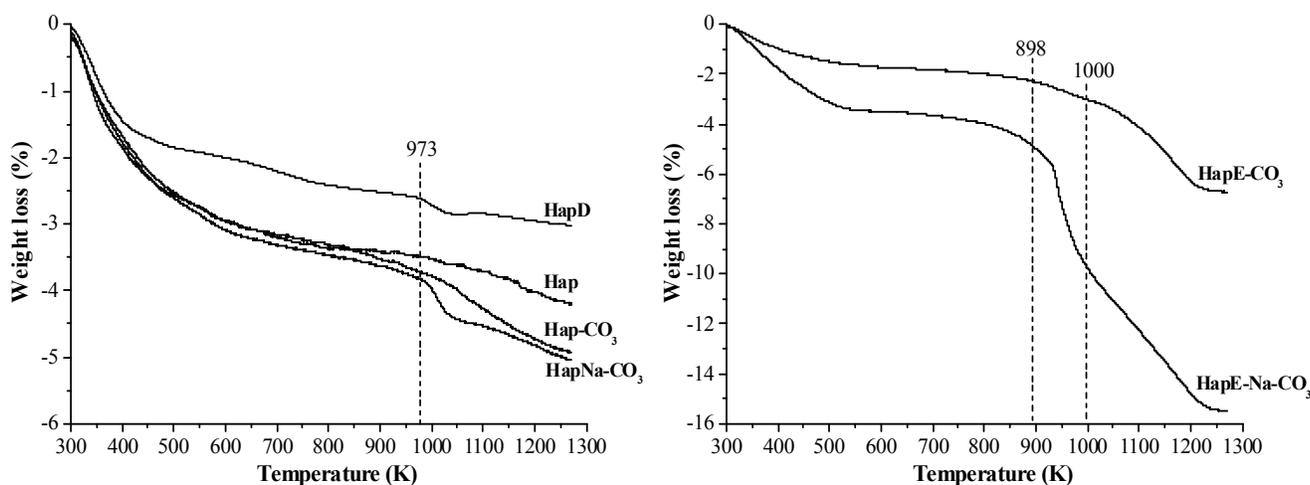


Fig.4 TGA curves showing the weight loss of the samples calcined at 673 K. The derived curves of CO<sub>2</sub> loss obtained by using mass spectrometer with  $m/z = 44$  are shown in Figure S5†.

These transformations were further examined by means of thermogravimetric analysis combined with mass spectrometry (Figure 4), confirming the aforementioned XRD results. For all the compositions, weight losses are due to the release of CO<sub>2</sub> and/or H<sub>2</sub>O as observed from the TPD-MS curves (Figures S5† & S6†). In agreement with previous works,<sup>24,37</sup> weight losses are attributed to the H<sub>2</sub>O and CO<sub>2</sub> desorption from the hydroxyapatite surface below 823 K and to the CO<sub>2</sub> released from the crystal above 923 K. Indeed, in this temperature range, as observed in the TPD-MS curves, the release of H<sub>2</sub>O is very low and its corresponding weight loss can be negligible. The thermograms can be divided into three groups, corresponding to the observed shapes of the recorded lines: (a) HapD and HapNa-CO<sub>3</sub>, (b) Hap and Hap-CO<sub>3</sub> and (c) HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>. In group (a), a clear transition was observed at 973 K in good agreement with the decomposition of HapD observed by X-ray diffraction (Figure S4(a)†). For the second group (b), the transition occurred at around the same temperature of 973 K, but was not sharp, and a plateau was not obtained at 1273 K. For carbonate-rich apatites

HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub> [group (c)], MS curves indicate surprisingly no departure of CO<sub>2</sub> before 873 K. The release of CO<sub>2</sub> in the HAPs started at a lower temperature, and occurred in two steps with a change in the slope around 1000 K, in good agreement with the high temperature X-ray diffraction study. Assuming that the decomposition of all the apatites led to stoichiometric HAP and CaO [except for HapD, for which this is Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> instead of CaO] at the end of the thermal study, it was possible to calculate the corresponding loss in CO<sub>2</sub> or, otherwise, of CO<sub>3</sub><sup>2-</sup> moles per apatite formula (Table 3). By comparison with the CO<sub>3</sub><sup>2-</sup> content in the B sites deduced from Rietveld refinement and the total CO<sub>3</sub><sup>2-</sup> loss obtained from TGA, the first mass loss was easily attributed to the release of CO<sub>3</sub><sup>2-</sup> from the A sites (channels) and the second mass loss to the release of CO<sub>3</sub><sup>2-</sup> from the B sites.

**Table 3** Carbonate mole content in the apatite solids of general formula  $\text{Ca}_{10-x}(\text{PO}_4)_6(\text{CO}_3)_x[(\text{OH})_y(\text{CO}_3)_z]$


Solids	$\text{CO}_3^{2-}$ in the A sites from TGA (z)*	$\text{CO}_3^{2-}$ in the B sites from TGA (x)**	$\text{CO}_3^{2-}$ in the B sites from XRD (x)
HapD	-	0.14	0.18(5)
Hap	-	0.21***	0.32(5)
Hap-CO <sub>3</sub>	-	0.40	0.37(5)
HapNa-CO <sub>3</sub>	-	0.36***	0.37(6)
HapE-CO <sub>3</sub>	0.30	0.83	0.64(9)
HapE-Na-CO <sub>3</sub>	1.47	1.43	1.28(9)

\* Deduced from the weight loss starting from 773 K;

\*\* Deduced from the weight loss starting from 973 K;

\*\*\* Underestimated since a plateau was not obtained.

Interestingly,  $\text{CO}_3^{2-}$  was mainly located in the B sites for HapD, Hap, Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub> and in both A and B sites for the carbonate-rich apatites, namely, HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>. It is worth mentioning that the carbonate content deduced from XRD and TGA were in good agreement with the ICP analysis, confirming the good precision and the reliability/accuracy of the XRD refinement (Table 3). Moreover, a linear increase was observed in the case B-type  $\text{CO}_3^{2-}$  obtained both from TGA and XRD as shown in Figure 5, in excellent agreement with the theoretical line.

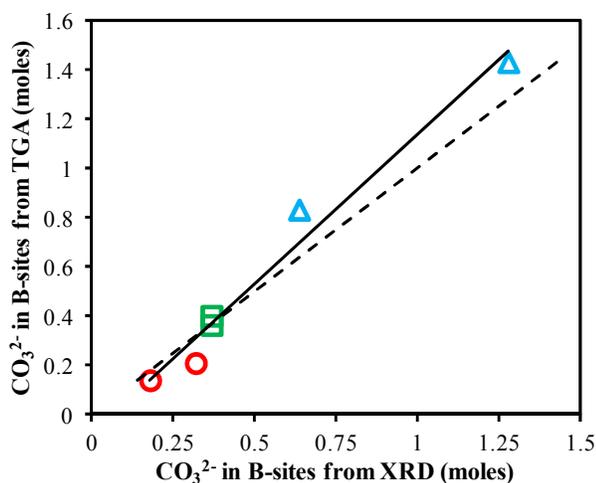


**Fig.5** Number of moles of  $\text{CO}_3^{2-}$  in B-sites obtained from TGA as a function of the same parameter obtained from XRD (circles representing HapD and Hap, squares for carbonated apatites, namely Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub>, and triangles for carbonate-rich apatites, namely HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>). The dashed line represents the theoretical perfect correlation (1 to 1 ratio).

### 3.3.3.2 A & B-type carbonates substitution


Figure 6 and Figure 7 represent two domains of the IR spectra of the HAP samples, focused on two different respective spectral regions, namely 700–1800  $\text{cm}^{-1}$  and 3300–3700  $\text{cm}^{-1}$ . All the IR spectra confirmed the formation of carbonates-containing apatites with bands at 872  $\text{cm}^{-1}$ , 1460  $\text{cm}^{-1}$  and 1419  $\text{cm}^{-1}$ .

The fundamental vibrational modes of  $\text{PO}_4$  species gave rise to bands at 565  $\text{cm}^{-1}$ , 605  $\text{cm}^{-1}$ , 963  $\text{cm}^{-1}$  and 1030–1100  $\text{cm}^{-1}$ , as reported earlier.<sup>41,42</sup> Further,  $\text{HPO}_4^{2-}$  groups might also be present, with the characteristic band at 872  $\text{cm}^{-1}$ . However, this latter is known to overlap with a carbonate band, making straightforward conclusions impossible.<sup>38</sup>

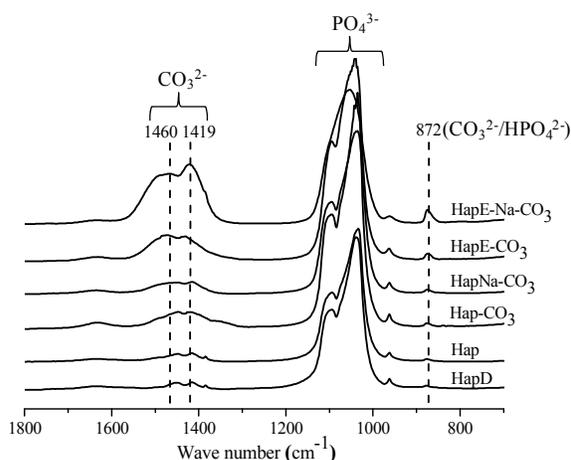

**Fig.6** IR spectra of HAPs in the 700-1800  $\text{cm}^{-1}$  region.

The broad vibrational band in the 3300-3700  $\text{cm}^{-1}$  range is due to the presence of adsorbed and constitutive water molecules. The presence of carbonates in B-sites was confirmed by the increase in the intensity of the typical band at 872  $\text{cm}^{-1}$  observed in carbonate-rich apatites,<sup>40,43</sup> which could make the presence of  $\text{HPO}_4^{2-}$  species quite questionable, but these latter were detected using NMR spectroscopy (see §3.4). In addition, the peaks at 1460  $\text{cm}^{-1}$  and 1419  $\text{cm}^{-1}$  can be attributed to  $\text{CO}_3^{2-}$  substituting  $\text{PO}_4^{3-}$  groups, which thus lead to the formation of B-type apatites.<sup>39</sup> The band at 3572  $\text{cm}^{-1}$  is assigned to structural OH groups. It is worth noticing that the intensity of this band was higher for all the apatites except for carbonates-rich apatites (Figure 7). It was almost not detected in HapE-Na-CO<sub>3</sub> and was not so significant in the case of the HapE-CO<sub>3</sub> sample, confirming also the A-type substitution of OH<sup>-</sup> by  $\text{CO}_3^{2-}$  ions in the carbonate-rich apatites.<sup>40</sup> So, the A-type substitution was especially evidenced when the carbonate content in the HAP was very high, which is in good agreement with the TGA results.

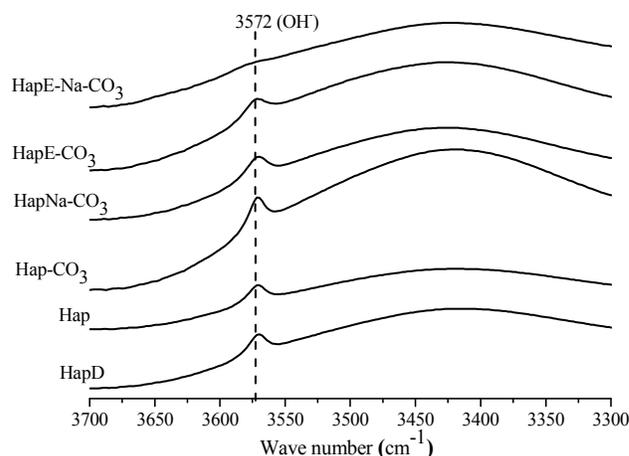

**Fig.7** IR spectra of HAPs of the carbonate apatites in the 3300-3700  $\text{cm}^{-1}$  region.

In brief, the IR spectra thus confirmed the A or/and B-type substitution by  $\text{CO}_3^{2-}$  groups in all the apatite solids, which was in agreement with the XRD and TGA observations.

### 3.4 Presence of $\text{HPO}_4^{2-}$ groups in the prepared solids

Since, it was not possible to clearly assess the presence of  $\text{HPO}_4^{2-}$  groups in the solids by using FTIR-spectroscopy,  $^1\text{H}$ - $^{31}\text{P}$  CP MAS-NMR was performed. This technique enables detecting the presence of P belonging to acidic  $\text{HPO}_4^{2-}$  groups and of P belonging to  $\text{PO}_4$  (orthophosphate) species.

All the samples exhibited a common signal resonating at 3.3 ppm due to  $\text{PO}_4^{3-}$  species (Figure S7†).<sup>43</sup> Moreover, the line shape of the peaks tended to vary with the carbonate content, carbonate-rich apatites giving rise to broader peaks. This phenomenon is due to the distortions or defects in the P

environment, resulting from the statistical carbonate substitution/removal of the ions in the apatite structure.<sup>44</sup> In addition to this signal, a broad peak centred at 6.5 ppm was clearly observed for HapD and Hap, which both contain a lower carbonate content compared to the other samples. For the other apatites, it was difficult to differentiate this signal due to its low intensity, and also because of the broadening of signal of the orthophosphate species at 3.3 ppm. This peak can be attributed to a distribution of phosphorus species due to the low content of carbonate.

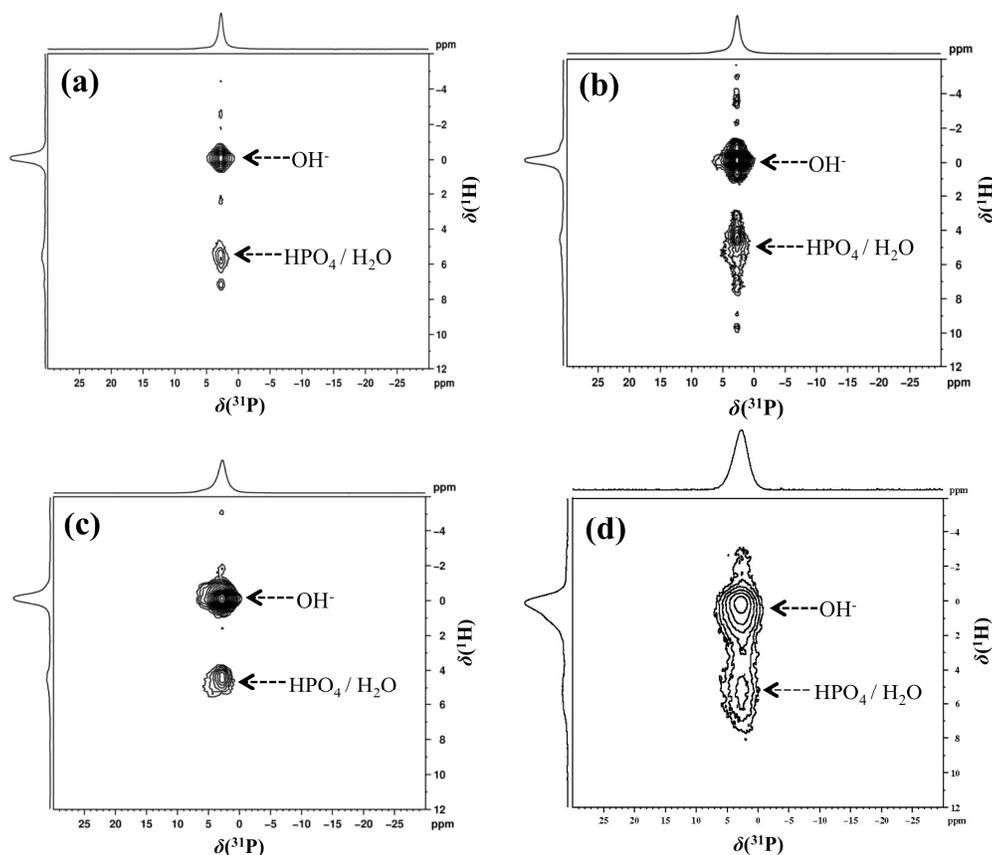


Fig.8 2D HETCOR spectra of (a) HapD, (b) Hap, (c) HapNa- $\text{CO}_3$ , and (d) HapE- $\text{Na-CO}_3$ .

In order to confirm the presence of  $\text{HPO}_4^{2-}$  groups in the materials, 2D  $^1\text{H}$ - $^{31}\text{P}$  heteronuclear correlation (HETCOR) spectrum were then recorded. Figure 8 shows the 2D spectra of the solids at the short contact time of 1 ms, at which the intensity of the signal due to  $\text{HPO}_4^{2-}$  groups is known to be more pronounced than the phosphorus signal in the close vicinity of  $\text{H}_2\text{O}$ .<sup>44</sup> The 2D spectra of all the solids clearly show a signal resonating at 0 ppm along the  $^1\text{H}$  axis due presence of the proton of  $\text{OH}^-$  that cross polarizes with P of phosphate groups, and a second signal resonating between 3 to 8 ppm along the  $^1\text{H}$  axis mainly due to protons from  $\text{HPO}_4^{2-}$  groups. This latter is also observed in 2D spectra recorded with a very short contact time of 150  $\mu\text{s}$  (not shown) corresponding to a selective time for short P-O-H distance, hence to  $\text{HPO}_4^{2-}$  groups.<sup>45</sup>

So, the presence of acidic  $\text{HPO}_4^{2-}$  groups was evidenced in all

the HAPs, irrespective of the Ca/P ratio. However, quantification was not possible with this technique, which remains qualitative.

### 3.5 Surface composition of the HAPs

#### 3.5.1 Surface Ca/P ratios and carbonate species

XPS analysis was then carried out to get surface information. The comparison of the Ca/P ratios and of the  $C_{\text{carbonates}}/\text{P}$  ratios determined by ICP, XRD/TGA and XPS are given in Table 4. Concerning the Ca/P ratios, the XPS surface analysis was in good agreement with the bulk analysis for all the solids, except for HapD and Hap. Surface Ca/P ratios of 1.19 in HapD and 1.27 in Hap were much lower than the bulk ratios, 1.62 and 1.69, respectively. This is in good agreement with previous studies<sup>3,46</sup> and indicates that, for these two compositions, Ca species are less exposed to the surface than phosphates, at least within the ca. 10 nm analysis depth limit of the XPS technique. For the other

samples, the surface Ca/P ratios increased from 1.66 (Hap-CO<sub>3</sub>) to 2.06 (HapE-Na-CO<sub>3</sub>) with the increase in the content of carbonate ions and turned out to be almost similar to bulk ratios.

The surface carbon-based species have been examined using the characteristics of the C 1s photopeak. The decomposition of the C 1s peak allowed us to evidence four components, corresponding namely to C-C, C-O and C=O bonds, as well as a

specific feature corresponding to CO<sub>3</sub><sup>2-</sup>, with respective binding energies of 285.0 (fixed reference), 286.5, 288.5 and 290.0 eV (Figure S8†). The relative intensity of the peaks attributed to species containing C-O, C=O was similar, irrespective of the sample with C-O/C=O ratios between 1.2 and 1.8, whereas the intensity of the CO<sub>3</sub><sup>2-</sup> species over the surface showed the global trend of increasing together with the CO<sub>3</sub><sup>2-</sup> content (Table 4).

**Table 4** Comparison of Ca/P & C<sub>carbonates</sub>/P atomic ratios in the apatites determined by ICP, XRD-TGA & XPS.


Solid	ICP Ca/P atomic ratio	XRD Ca/P atomic ratio (% difference relative to ICP)	XPS Ca/P atomic ratio (% difference relative to ICP)	ICP C <sub>carbonates</sub> /P atomic ratio	XRD-TGA C <sub>carbonates</sub> /P atomic ratio	XPS C <sub>carbonates</sub> /P atomic ratio
HapD	1.62	1.71 (+ 5.5%)	1.19 (- 26.5%)	0.03	0.02	0.07
Hap	1.69	1.76 (+ 4.1%)	1.27 (- 24.9%)	0.06	0.04*	0.10
Hap-CO <sub>3</sub>	1.70	1.77 (+ 4.1%)	1.66 (- 2.4%)	0.09	0.07	0.21
HapNa-CO <sub>3</sub>	1.72	1.78 (+ 4.7%)	1.67 (- 2.9%)	0.10	0.06*	0.14
HapE-CO <sub>3</sub>	1.90	1.86 (- 2.1%)	1.81 (- 4.7%)	0.22	0.21	0.14
HapE-Na-CO <sub>3</sub>	2.39	2.12 (- 11.3%)	2.06 (- 13.8%)	0.59	0.61	0.23

\* underestimated since a plateau was not obtained.

Previous studies have shown that a variation in the Ca/P ratio in HAPs drastically changes their chemical properties.<sup>3</sup> Likewise, the solids prepared with different Ca/P surface ratios, and, furthermore, exhibiting different C<sub>carbonates</sub>/P ratios should exhibit different surface properties, depending in part on the amount of carbonates present on their surface – or, at least, adsorbable at their surface. This will be checked later on in the present paper when examining the acid-base properties of the solids.

As a partial conclusion for this part, while for all the samples the C<sub>carbonates</sub>/P ratios obtained from XRD/TGA were comparable and in rather good agreement with the C<sub>carbonates</sub>/P ratios obtained from ICP (Table 4), the C<sub>carbonates</sub>/P ratio determined by XPS was not consistent, underlining the surface complexity in hydroxyapatite solids.


### 3.5.2 Composition of outermost atomic layer of the samples

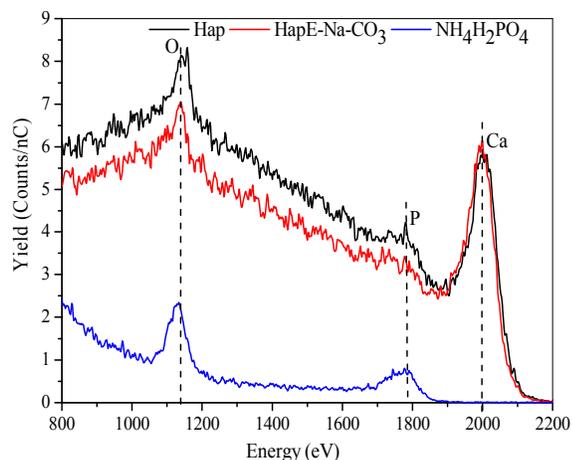

**Fig.9** LEIS spectra of selected apatite solids.

To get insights on the elemental composition in the first atomic layer of solids, LEIS is a very sensitive technique. To verify whether the Ca/P ratio or the carbonate content affects the topmost surface atomic distribution, stoichiometric Hap (low Ca/P ratio and carbonate content) and HapE-Na-CO<sub>3</sub> (high Ca/P ratio and carbonate content) were chosen for analysis (Figure 9). For Hap and HapE-Na-CO<sub>3</sub>, two surface peaks due to Ca and O are clearly observed at 2000 eV and 1135 eV, respectively. A surface peak due to P is observed at 1790 eV, but is overlapped by the background signal resulting from the secondary ions background and/or the in-depth signal of Ca present from deeper layers. To clearly assess the expected position of a peak due to P, LEIS was performed using NH<sub>4</sub>H<sub>2</sub>PO<sub>4</sub> as a standard, which is a precursor used in the hydroxyapatites synthesis. A signal is clearly observed at 1790 eV, thus confirming the presence of P on the apatites surfaces. Despite the poor intensity of the phosphorous peak, it is worth noting that it is less intense for HapE-Na-CO<sub>3</sub> than for Hap. These results suggest that Ca ions and O ions are more exposed to the first atomic layer of hydroxyapatites, irrespective of the Ca/P ratio (1.69 & 2.39) and of the carbonate content (0.40 & 2.95 wt.%) in Hap and HapE-Na-CO<sub>3</sub>, respectively. This may contradict the results obtained by XPS, which showed a lower Ca/P ratio for Hap. However, we have to remind that the LEIS technique only probes the topmost atomic layer of the samples, while XPS gives information on the composition, but along a depth of a few nanometers. The O atoms of the first atomic layer belong to PO<sub>4</sub><sup>3-</sup>, CO<sub>3</sub><sup>2-</sup> and CaO/Ca-O species present at the surface of the apatites. So, we could also propose that the surface of the hydroxyapatite crystallites mainly consists of Ca species rather than P species. Since the results obtained from Rietveld refinements have shown that the crystallite growth is more along the [0 0 1] direction or in the *c*-axis direction, the Ca ions should be more exposed along the *c*-axis, that is, on *ac* and *bc* planes. A schematic representation of


the two possible crystallite surface cleavages is shown in Figure 10. According to the above results, we then suppose that, in our study, the apatite crystallites are mainly cleaved in such a way that Ca atoms are more exposed to the surface, represented by the green line in Figure 10.

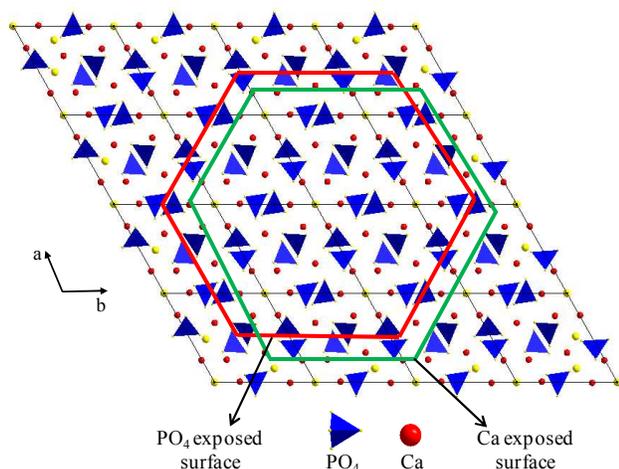

**Fig.10** Schematic representation of the hydroxyapatite lattice: The green line shows the crystallite surface cleavage through Ca atoms, which is actually occurring according to our study, and the red line shows the theoretical crystallite cleavage through P atoms that is another possibility, but not predominant in our solids.

### 3.6 Acid-base properties of the solids

#### 3.6.1 Acid sites number, nature, and relative distribution

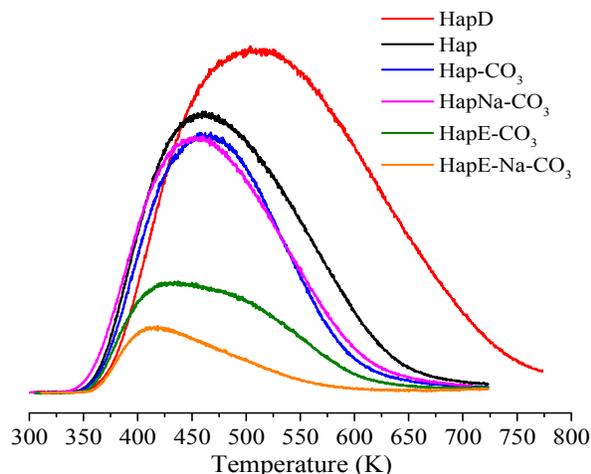

**Table 5** Number, nature and distribution of acid sites determined by NH<sub>3</sub>-TPD and PEA-XPS.

Solids	Number of acid sites ( $\mu\text{mol.g}^{-1}$ )	Specific acidity ( $\mu\text{mol.m}^{-2}$ )	Nature & distribution of acid sites	
			Lewis ( $\mu\text{mol.m}^{-2}$ )	Bronsted ( $\mu\text{mol.m}^{-2}$ )
HapD	956	7.73	5.16 (66.7%)	2.57 (33.3%)
Hap	763.3	6.73	5.43 (80.7%)	1.30 (19.3%)
Hap-CO <sub>3</sub>	658	6.13	5.58 (91.1%)	0.54 (8.9%)
HapNa-CO <sub>3</sub>	604	5.53	5.17 (93.5%)	0.36 (6.5%)
HapE-CO <sub>3</sub>	324	4.27	4.01 (94%)	0.26 (6%)
HapE-Na-CO <sub>3</sub>	141.3	1.87	1.78 (95.3%)	0.09 (4.7%)

We saw above that the crystallite growth along the *c*-axis ([0 0 1] direction) increased with the carbonate content, which means that

**Fig.11** NH<sub>3</sub>-TPD curves of the apatite solids.

Figure 11 shows the NH<sub>3</sub>-TPD curves for all the apatite solids. It clearly appears that the peak corresponding to the deficient apatite HapD is much broader exhibited the highest Full Width at Half Maximum (FWHM) value of 497 K. In addition, the maximum of the peak of HapD was shifted to a higher desorption temperature (513 K) compared to the other solids. This reflects the presence of stronger acid sites in a very broad temperature range extending up to 773 K. The FWHM decreased further to 435 K for Hap, whose peak is broadened up to a desorption temperature of 698 K. The FWHM was lowered for carbonated apatites Hap-CO<sub>3</sub> (410 K) and HapNa-CO<sub>3</sub> (412 K) compared to more acidic apatites HapD and Hap, but these samples still possessed acid sites of a relatively high strength, of which the desorption temperature extended up to 623 K. The intensity of the signals obtained for carbonate-rich apatites was clearly lower compared to that of the other apatites, though the desorption temperature extended up to 623 K, similarly to that of the carbonated apatites. Hence, Hap and especially HapD show their predominant acidic character with stronger acid sites compared to other apatites.

The total number of acid sites in the samples was determined by integrating the NH<sub>3</sub>-TPD profiles and the results are gathered in Table 5. The specific acidity of the apatites decreased rather linearly from 7.73 to 1.87  $\mu\text{mol.m}^{-2}$  with the increase in the Ca/P surface ratio and the surface carbonate content, as shown in Figure S9†. The variation in the specific acidity can be linked with many parameters, such as the crystallites morphology, the surface Ca/P ratio, and the quantity of surface HPO<sub>4</sub><sup>2-</sup>, CO<sub>3</sub><sup>2-</sup>, CaO species, resulting from the replacement of PO<sub>4</sub><sup>3-</sup>/OH<sup>-</sup> groups.<sup>3,46</sup> It has been observed from LEIS that Ca<sup>2+</sup> (Lewis acid sites) present in *ac* and *bc* unit cell faces of apatites become more exposed to the surface if crystallite grows along the [0 0 1] direction, which is in good agreement with previous reports.<sup>47,48</sup>

the carbonate-rich apatites, which have a larger crystallite size along the *c*-axis, should possess more acid sites due to the exposure of a larger amount of  $\text{Ca}^{2+}$  species. Instead, carbonate-rich apatites presented a lower density in acid sites, maybe because most of the Ca exists under the form of CaO or Ca-O<sup>-</sup> species present at the surface due to excess Ca/P ratio in carbonate-rich apatite solids. The Ca  $2p_{3/2}$  XPS peak of carbonate-rich apatites was broadened with higher FWHM compared with the peak of stoichiometric Hap (data not shown), most probably due to the presence of CaO. Moreover, the high temperature XRD showed peaks due to CaO species, which are more predominant in carbonate-rich apatites. So, we suppose that the CaO phase might also be present in all the apatite solids at room temperature, but in a highly dispersed – surface – state, similarly to recent findings on Sr apatites, which evidenced the presence of highly dispersed SrO species.<sup>49</sup> HapD has a higher number of acid sites due to the contribution from  $\text{HPO}_4^{2-}$  groups or  $\text{OH}^-$  vacancies, which are more numerous in deficient apatites and in good agreement with previous reports.<sup>3</sup>

PEA-XPS investigation of the apatite surfaces was used as a complementary way to the TPD approach to determine the Brønsted or Lewis nature of the surface acid sites, as previously reported.<sup>22,49</sup> The PEA-XPS spectra of all the samples presented a broad N 1s peak centered at binding energies in the 396.5 - 405.0 eV range, which could be decomposed into two peaks, at BEs of 398.0 - 405.0 eV and 396.5 - 403.5 eV, thus revealing the presence of Brønsted and Lewis acid sites, respectively (Figure 12). Also, it has been reported that the basic probe can be retained

on Brønsted sites by the formation of an ammonium cation and on Lewis sites by the formation of a complex.<sup>22,50</sup> Taking into account the hydroxyapatite surface, we propose that the ammonium cation can be formed with PEA mainly on acidic  $\text{HPO}_4^{2-}$  groups present on the HAP surface and the complex formation can take place over  $\text{Ca}^{2+}$  or over  $\text{OH}^-$  vacancies ( $\delta^+$ ) (Figure 13).

Hence, in all the HAPs,  $\text{HPO}_4^{2-}$  groups act as Brønsted acid sites and  $\text{Ca}^{2+}$ /vacancies as Lewis acid sites. The obtained relative distribution of Lewis and Brønsted acid sites is reported in Table 5 together with the specific amount of each site.

Irrespective of the sample, the contribution of the Lewis acid sites was dominant and varied between 66.7% and 95.3%. PEA-XPS showed that all the solids possess Brønsted  $\text{HPO}_4^{2-}$  groups irrespective of the Ca/P ratio, which is in good agreement with the 2D-NMR results. More  $\text{HPO}_4^{2-}$  groups present in HapD resulted in the presence of more Brønsted sites, when compared to the other samples. Contribution from Brønsted  $\text{HPO}_4^{2-}$  groups was lower in carbonate-rich HAPs compared with the other solids, which supposedly results from the substitution of  $\text{OH}^-/\text{PO}_4^{3-}$  by  $\text{CO}_3^{2-}$  group, required to counterbalance the charge.<sup>47</sup> For carbonate-rich apatites, there is also an observable decrease in the number of Lewis acid sites ( $\text{Ca}^{2+}$ ) compared to the other apatites, though they possess higher Ca/P ratios compared to the other apatites. This decrease in the number of Lewis acid sites can be due to the formation of CaO species over the carbonate-rich apatites, which are no more Lewis acid sites, but consequently leave basic sites on the surface.

Cite this: DOI: 10.1039/c0xx00000x

FULL PAPER

www.rsc.org/xxxxxx

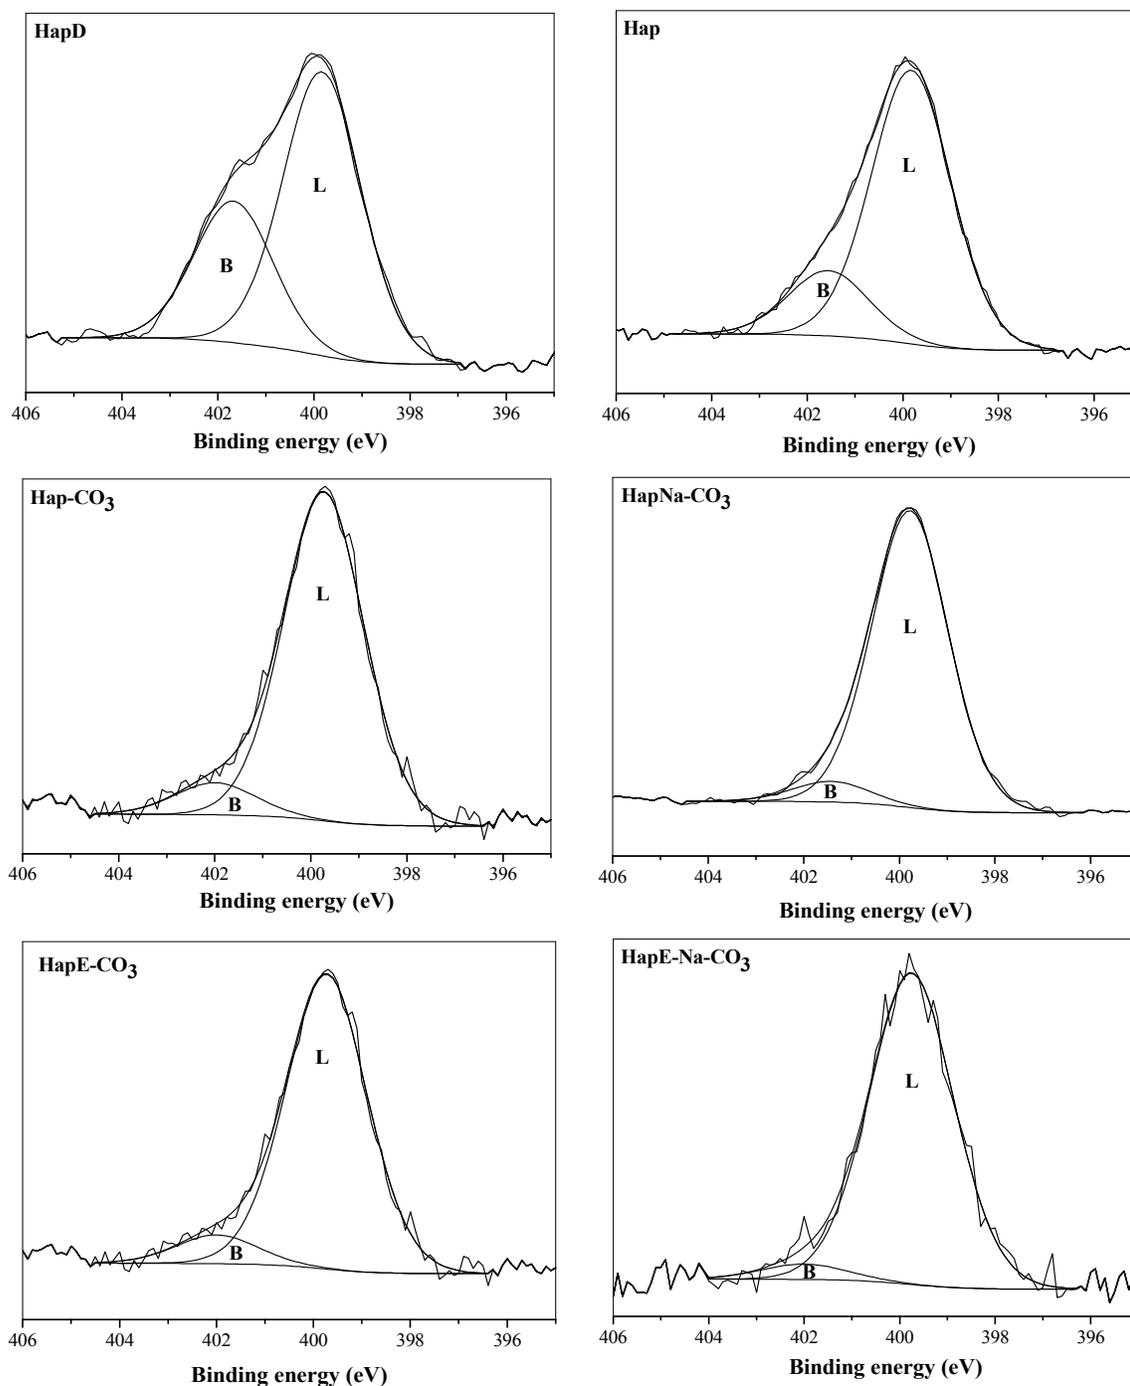


Fig.12 Decomposition of the N 1s photopeak after PEA adsorption on the apatite solids surface.

Hence, the HapD and Hap have much more contribution of 33.3% and 19.3%, respectively, from the Brønsted acid sites

compared to all the other apatites, whose Brønsted acid sites contribution varies between 4.7% (HapE-Na-CO<sub>3</sub>) and 8.9%

(Hap-CO<sub>3</sub>). For HapD and Hap, this larger contribution of Brønsted acid sites is linked with the observation of higher FWHMs of 497 K and 435 K, respectively, of their NH<sub>3</sub>-TPD

profiles, so that we can deduce that, on these samples, strong Brønsted acid sites are created.

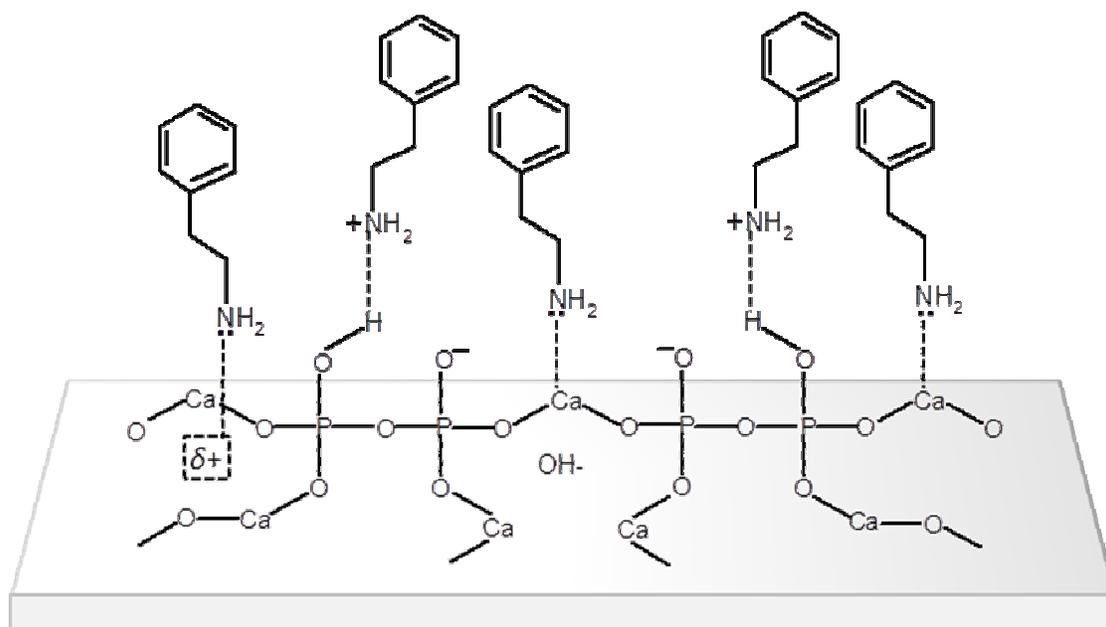


Fig.13 Model of PEA adsorption over Lewis and Brønsted acid sites on the surface of apatites. [( $\delta+$ ) = OH<sup>-</sup> vacancies].

### 3.6.2 Number and distribution of basic sites

Basic sites with at least three different strengths can be distinguished from the CO<sub>2</sub>-TPD profiles (Figure 14). The main contribution to the CO<sub>2</sub> desorption peak seems to be due to weak basic sites with a maximum observed at  $398 \pm 10$  K over all the apatites. A second peak at around 493 K due the presence of basic sites of a medium strength is also observed, more clearly for HapNa-CO<sub>3</sub> and Hap-CO<sub>3</sub> with a more intense signal. A last peak is observed at around 613 K, due to the presence of strong basic sites for Hap, Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub>. This peak was observed neither in the deficient apatite HapD nor in the carbonate-rich apatites (HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>). Since the carbonate-rich apatites are the solids that have shown the A-type substitution of CO<sub>3</sub><sup>2-</sup> replacing the OH<sup>-</sup> groups, we suppose that the absence of the peak due to stronger basic sites arises from the lack in basic OH<sup>-</sup> species. It is known that in the case of deficient apatites (here, HapD), deficiency of Ca<sup>2+</sup> ions is compensated by the addition of H<sup>+</sup> and removal of OH<sup>-</sup> ions, and this may be the reason for the absence of OH<sup>-</sup> peaks in HapD. But, further investigations are needed to confirm this assumption of OH<sup>-</sup> as stronger basic sites.

The amount of basic sites was determined by integrating the TPD profile of CO<sub>2</sub> (Table 6). The number of basic sites tended to increase from  $6.2 \mu\text{mol.g}^{-1}$  to  $23.3 \mu\text{mol.g}^{-1}$  when the Ca/P ratio or the carbonate content increased from HapD to HapNa-CO<sub>3</sub>, and then decreased with further increase in the Ca/P ratio or carbonate content in carbonate rich apatites.

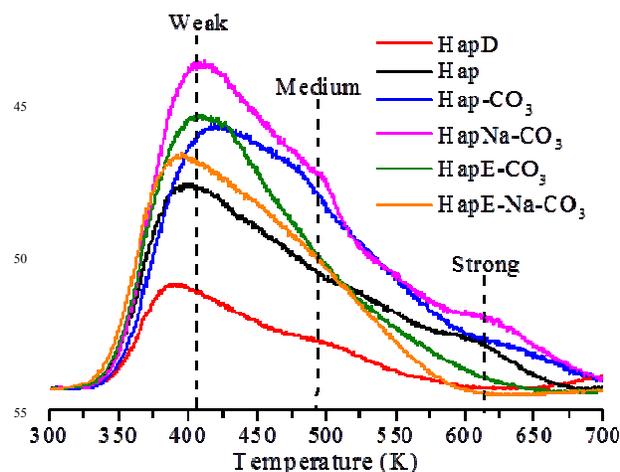


Fig.14 CO<sub>2</sub>-TPD profiles of the apatite solids.

In contrast, the specific basicity increased from  $0.05 \mu\text{mol.m}^{-2}$  to  $0.21 \mu\text{mol.m}^{-2}$  when the Ca/P ratio or the carbonate content increased from HapD to HapNa-CO<sub>3</sub> and remained almost unchanged with further increase in the Ca/P ratio, namely in carbonate-rich apatites, HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>.

Benzoic acid adsorption using a pulse liquid chromatographic technique<sup>23</sup>, a complementary technique to TPD-CO<sub>2</sub>, was also employed to determine the distribution of strong and weak basic sites. Specific basicity determined by benzoic acid adsorption show somewhat different results compared to the TPD-CO<sub>2</sub> technique. Contrary to the lower amount of basic sites in HapD ( $0.33 \mu\text{mol.m}^{-2}$ ) compared with Hap ( $0.87 \mu\text{mol.m}^{-2}$ ) as determined by TPD-CO<sub>2</sub>, the benzoic acid adsorption resulted in higher amounts of basic sites in HapD ( $2.09 \mu\text{mol.m}^{-2}$ ) than in


stoichiometric Hap ( $1.70 \mu\text{mol.m}^{-2}$ ). Considering the carbonated apatites, Hap-CO<sub>3</sub> owns specific basic sites of  $4.66 \mu\text{mol.m}^{-2}$ , but HapNa-CO<sub>3</sub> ( $1.24 \mu\text{mol.m}^{-2}$ ) has the lowest amount of specific basic sites compared to all the other apatites. Specific basicity observed for carbonate-rich apatites HapE-CO<sub>3</sub> ( $4.08 \mu\text{mol.m}^{-2}$ ) and HapE-Na-CO<sub>3</sub> ( $4.88 \mu\text{mol.m}^{-2}$ ) were higher than for all the

other apatites except for Hap-CO<sub>3</sub>, which has more basic sites than HapE-CO<sub>3</sub>. The highest amount of basic sites obtained using benzoic acid determination once again confirms the presence of 10 CaO species in carbonate-rich apatites.

**Table 6** Basic sites distribution determined by TPD-CO<sub>2</sub> and benzoic acid adsorption.

Solids	Ca/P atomic ratio (ICP)	TPD-CO <sub>2</sub>		Benzoic acid adsorption			
		Total basic sites ( $\mu\text{mol.g}^{-1}$ )	Specific basicity ( $\mu\text{mol.m}^{-2}$ )	Total basic sites ( $\mu\text{mol.g}^{-1}$ )	Specific basicity ( $\mu\text{mol.m}^{-2}$ )	Strong basic sites ( $\mu\text{mol.m}^{-2}$ )	Weak basic sites ( $\mu\text{mol.m}^{-2}$ )
HapD	1.62	41.33	0.33	259.9	2.09	1.88	0.21
Hap	1.69	100.67	0.87	194.3	1.70	1.45	0.25
Hap-CO <sub>3</sub>	1.70	136	1.27	499.5	4.66	4.66	0
HapNa-CO <sub>3</sub>	1.72	155.33	1.4	134.7	1.24	0.83	0.41
HapE-CO <sub>3</sub>	1.90	112.67	1.47	310.4	4.08	3.60	0.48
HapE-Na-CO <sub>3</sub>	2.39	104	1.47	351.6	4.88	4.29	0.59

### 15 3.6.3 Acid-base reactivity of the HAPs

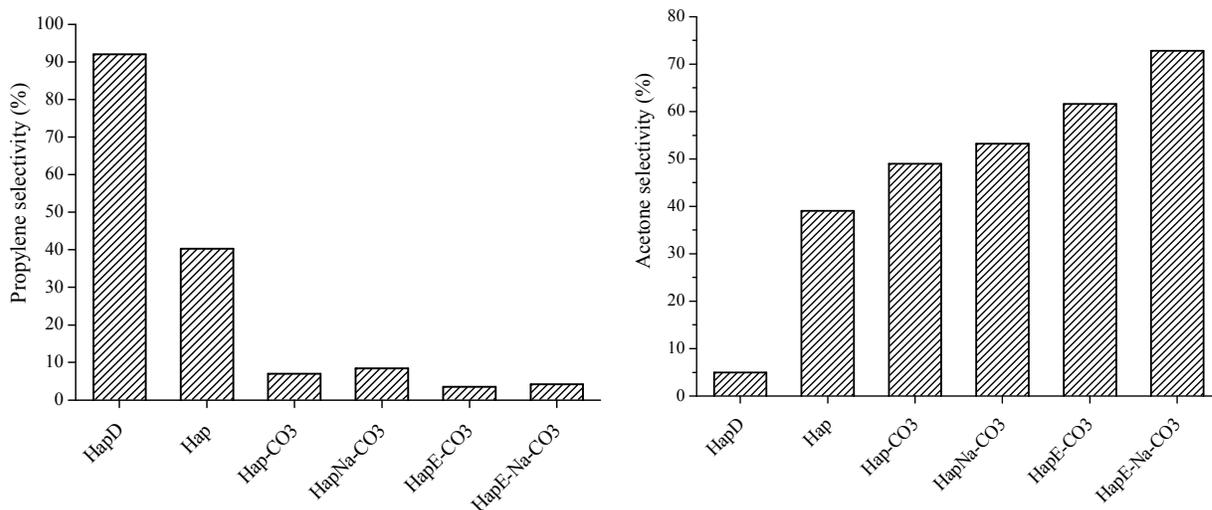

**Fig.15** Selectivity to propylene and acetone at 20% conversion of *isopropanol* in the presence of the apatite solids.


*Isopropanol* tests were performed at an *isopropanol* conversion of 20% and the variation in propylene and acetone distribution over the HAPs is shown in Figure 15. The catalytic conversion of *isopropanol* over all the apatites yielded propylene, acetone, *di-isopropyl* ether and negligible amount of dienes. Acetone can be formed over basic sites and propylene and *di-isopropyl* ether over acid sites, as previously reported. The propylene formation was much higher over HapD and Hap compared to all the other apatites, underlining the acidic behavior of these catalysts, which is in good agreement with TPD-NH<sub>3</sub> and PEA-XPS. The high amount of acid sites and the presence of more Brønsted acid sites (HPO<sub>4</sub><sup>2-</sup> groups) with higher strength in HapD and Hap can explain this predominant formation of propylene. The propylene selectivity was lowered from 92% to 40.3% with increase in Ca/P ratio from 1.62 in HapD to 1.69 in Hap, but Hap still possessed a relatively high acidic character compared to the other catalysts. For carbonated apatites, Hap-CO<sub>3</sub> (Ca/P = 1.70) and HapNa-CO<sub>3</sub>

(Ca/P = 1.72), the propylene formation was then drastically reduced to 7% and 8.4%, respectively. This shows decrease in the acidic behaviour of HAPs with increase in Ca/P ratio or carbonate amount above a certain limit. Selectivity to propylene was further lowered to 3.5% and 4.2%, respectively for carbonate-rich apatites HapE-CO<sub>3</sub> (Ca/P = 0.90) and HapE-Na-CO<sub>3</sub> (Ca/P = 2.39), showing the lack in acidic nature of apatites with very high Ca/P ratios or carbonate contents.

Selectivity to acetone tended to increase readily with the increase in the Ca/P ratio from HapD to HapE-Na-CO<sub>3</sub>. HapD with lower Ca/P ratio of 1.62 was less selective to acetone (5%) than all the other apatites, which is in good agreement with the lower number of basic sites ( $6.2 \mu\text{mol.g}^{-1}$ ) over this sample. Selectivity to acetone considerably increased to 39% in Hap (Ca/P = 1.69). Further increase in the Ca/P ratio for carbonated apatites, namely Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub>, led to an increase in the acetone selectivity to 49%, and 53.2%, respectively. While

the carbonate-rich solids, HapE-CO<sub>3</sub> (Ca/P = 1.90) and HapE-Na-CO<sub>3</sub> (Ca/P = 2.39) possess a lower number of basic sites compared to carbonated apatites, they have shown higher selectivity to acetone compared to all the other apatites. This can be due to the presence of more basic CaO species over carbonate-rich apatites, which enhance the dehydrogenation of *isopropanol* to acetone. Comparing the carbonate-rich apatites HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>, the latter was found to be more selective to acetone, though it possesses a lower amount of basic sites

10 compared to HapE-CO<sub>3</sub>. This can be thus due to formation of more CaO species over HapE-Na-CO<sub>3</sub> compared to HapE-CO<sub>3</sub>. It is also worth noting that, though catalysts Hap, Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub> possess stronger basic sites, they have shown lower selectivity to acetone compared to carbonate-rich apatites, which lack in stronger basic sites. This might indicate that dehydrogenation of *isopropanol* to acetone probably mainly took place over weak or medium basic sites.

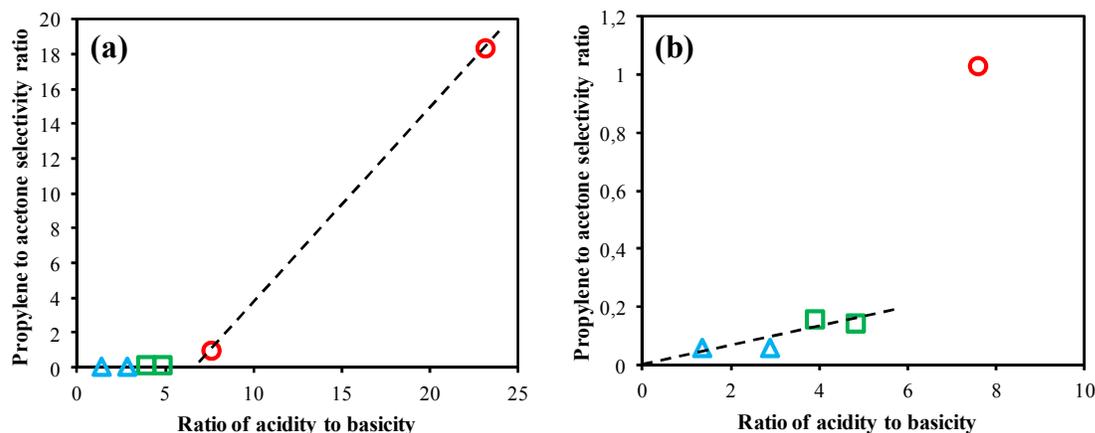

**Fig.16** (a) Ratio of propylene to acetone selectivity as a function of the ratio between the number of acid sites to the number of basic sites and (b) Same figure focused on a narrower range of acidity/basicity ratio (red circles representing HapD and Hap, green squares for carbonated apatites, namely Hap-CO<sub>3</sub> and HapNa-CO<sub>3</sub>, and blue triangles for carbonate-rich apatites, namely HapE-CO<sub>3</sub> and HapE-Na-CO<sub>3</sub>).

The plot of the propylene/acetone selectivity ratio (indirectly representing the acid/base behavior) as a function of the number of acid sites to the number of basic sites (direct acid-base behavior) is shown in the Figure 16. Hap and HapD clearly show a deviation (represented by dashed line) from the other apatites, which can be related to their higher acidic behavior (Figure 16 (a)). In addition, a rather linear increase in the propylene/acetone selectivity ratio with the acidity/basicity ratio (dashed line in Figure 16 (b)) was observed for carbonated and carbonate-rich apatites. Then, a remarkable correlation is observed between the *isopropanol* reactivity and acid-base properties for these samples. Formation of *di-isopropyl* ether was observed in small amounts, 2% in HapD and 0.9 % in Hap and trace amounts (below the quantification limit of *ca.* 0.5%, with a slightly visible GC peak quite mixed with the background and thus not exploitable) over the other apatites.

As a conclusion to this part, HapD and Hap have shown their predominant acidic behaviour compared to all the other apatites, which have shown much lower propylene selectivities. This predominant acidic behaviour is mainly due to the presence of stronger acid sites, especially of the Brønsted type. Presence of highly dispersed basic CaO species created from excess Ca/P ratio than stoichiometric value (1.67) could be the reason for the higher acetone selectivity over carbonate-rich apatites. Also, the results suggest that dehydrogenation of *isopropanol* to acetone takes place over weak and medium basic sites - and not over the stronger basic sites.

## Conclusions

Hydroxyapatites with different Ca/P ratios were successfully

synthesized using a precipitation method, optionally containing also Na<sup>+</sup> cations, and were extensively characterized.

Their carbonate content increased linearly with the Ca/P ratio. The occupancy of atoms was calculated using Rietveld refinement, and the so-obtained (Ca + Na)/P ratios were in good agreement with those obtained from ICP. A good correlation was further observed between the anisotropic crystallite shape obtained from XRD and the grain shape observed in SEM. Global tentative formulae for the apatites were deduced from the amount of CO<sub>3</sub><sup>2-</sup> substituted in the OH<sup>-</sup> sites (A-type) and the PO<sub>4</sub><sup>3-</sup> sites (B-type): (Ca<sub>10-x</sub>[(PO<sub>4</sub>)<sub>6-x</sub>(CO<sub>3</sub>)<sub>x</sub>][(OH)<sub>y</sub>(CO<sub>3</sub>)<sub>z</sub>]). LEIS showed that Ca<sup>2+</sup> is more exposed at the topmost surface of the apatite solids, irrespective of the Ca/P ratio. Combining the results of XRD refinement and LEIS, we proposed that Ca<sup>2+</sup> are more exposed along the (0 0 1) direction on the *ac* and *bc* planes. The presence of HPO<sub>4</sub><sup>2-</sup> entities suggested by IR spectra was confirmed in all the apatites using 2D NMR (HETCOR sequence). Further, PEA-XPS proved that HPO<sub>4</sub><sup>2-</sup> species act as Brønsted acid sites, and Ca<sup>2+</sup> or OH<sup>-</sup> vacancies ( $\delta^+$ ) as Lewis acid sites. The acid-base reactivity of the solids was subsequently determined using *isopropanol* reactivity, which gave selectivity results in good agreement with the acid-base properties directly obtained using NH<sub>3</sub>-TPD, PEA-XPS, and CO<sub>2</sub>-TPD. As a remarkable feature, HapD (deficient apatite) and Hap (stoichiometric apatite) showed a much more pronounced acidic behavior than that of the other apatites.

Further, the solids presented in the present study were used in the Guerbet reaction, which requires the presence of both acid and basic sites, and showed different reactivities in agreement with the results of the present paper.<sup>51</sup>

## Acknowledgements

The research leading to these results has received funding from the European Union Seventh Framework Programme (FP7/2007-2013) under grant agreement n°241718 EuroBioRef.

The "Fonds Européen de Développement Régional (FEDER)", "CNRS", "Région Nord-Pas-de-Calais" and "Ministère de l'Education Nationale de l'Enseignement Supérieur et de la Recherche" are acknowledged for fundings of X-ray diffractometers, NMR spectrometers and the regional platform of surface analysis.

The French-Italian research project PHC Galilée n°25955PK (2011–2012) is acknowledged for its financial support.

The authors also want to warmly thank Dr. Arnaud Beaurain and Mrs. Martine Trentesaux for their technical help on XPS spectra recording, Dr. Franco Finol for his help on PEA-XPS experiments, and, finally, Mr. Olivier Gardoll for his technical help on NH<sub>3</sub>-TPD and ATG-ATD experiments.

## Notes and references

<sup>a</sup> Université Lille Nord de France, 59000 Lille, France. E-mail: franck.dumeignil@univ-lille.fr, Fax: +33(0)3 20 43 65 61; Tel: +33(0)3 20 43 45 38.

<sup>b</sup> CNRS UMR 8181, Unité de Catalyse et Chimie du Solide, Cité scientifique, Bâtiment C3, 59655 Villeneuve d'Ascq, France.

<sup>c</sup> ENSCL, Villeneuve d'Ascq, F-59655, France.

<sup>d</sup> Dipartimento di Chimica, Università degli Studi di Milano, Via Golgi 19, 20133 Milan, Italy.


<sup>e</sup> Institut Universitaire de France, Maison des Universités, 103 Boulevard Saint-Michel, 75005 Paris, France.

† Electronic Supplementary Information (ESI) available: Examples of XRD diffractograms refinement; Temperature-programmed XRD; Derived ATG profiles; 11P CP MAS-NMR spectra. See DOI: 10.1039/b000000x/

- 1 J.C. Elliott, Structure and Chemistry of the Apatites and Other Calcium Orthophosphates, Elsevier: Amsterdam (1994).
- 2 S. Koutsopoulos, Synthesis and characterization of hydroxyapatite crystals: A review study on the analytical methods, *Journal of Biomedical Materials Research*, vol 62 (2002) p. 600-612.
- 3 T. Tsuchida, J. Kubo, T. Yoshioka, S. Sakuma, T. Takeguchi, W. Ueda, Reaction of ethanol over hydroxyapatite affected by Ca/P ratio of catalyst, *Journal of Catalysis*, vol 259 (2008) p. 183-189.
- 4 L.C. Kibby, K.W. Hall, Studies of acid catalyzed reactions: XII. Alcohol decomposition over hydroxyapatite catalysts, *Journal of Catalysis*, vol 29 (1973) p. 144-159.
- 5 S.J. Joris, C.H. Amberg, Nature of deficiency in nonstoichiometric hydroxyapatites I. Catalytic activity of calcium and strontium hydroxyapatites, *Journal of Physical Chemistry*, vol 75 (1971) p. 3167-3171.
- 6 T. Tsuchida, S. Sakuma, T. Takeguchi, W. Ueda, Direct Synthesis of n-Butanol from Ethanol over Nonstoichiometric Hydroxyapatite, *Industrial & Engineering Chemistry Research*, vol 45 (2006) p. 8634-8642.
- 7 A. Sohly, R. Tahir, S. Sebti, R. Skouta, M. Bousmina, M. Zahouily, M. Larzek, Efficient synthesis of chalcone derivatives catalyzed by re-usable hydroxyapatite, *Applied Catalysis A: General*, vol 374 (2010) p. 189-193.
- 8 S. Sebti, R. Tahir, R. Nazih, S. Boulaajaj, Comparison of different Lewis acid supported on hydroxyapatite as new catalysts of Friedel-Crafts alkylation, *Applied Catalysis A: General*, vol 218 (2001) p. 25-30.
- 9 C.L. Kibby, K.W. Hall, Dehydrogenation of alcohols and hydrogen transfer from alcohols to ketones over hydroxyapatite catalysts, *Journal of Catalysis*, vol 31 (1973) p. 65-73.

- 10 N. Cheikhi, M. Kacimi, M. Rouimi, M. Ziyad, L.F. Liotta, G. Pantaleo, G. Deganello, Direct synthesis of methyl isobutyl ketone in gas-phase reaction over palladium-loaded hydroxyapatite, *Journal of Catalysis*, vol 232 (2005) p. 257-267.
- 11 T.J. Webster, E.A. Massa-Schlueter, J.L. Smith, B.E. Slamovich, Osteoblast response to hydroxyapatite doped with divalent and trivalent cations, *Biomaterials*, vol 25 (2004) p. 2111-2121.
- 12 S. Shimoda, T. Aoba, E. Morenoe, Y. Miake, Effect of Solution Composition on Morphological and Structural Features of Carbonated Calcium Apatites, *Journal of Dental Research*, vol 69 (1990) p. 1731-1740.
- 13 T.S.B. Narasaraju, D.E. Phebe, Some physico-chemical aspects of hydroxyapatite, *Journal of Materials Science*, vol 31 (1996) p. 1-21.
- 14 S. Kannan, J.H.G. Rocha, J.M.F. Ferreira, Synthesis and thermal stability of sodium, magnesium co-substituted hydroxyapatites, *Journal of Materials Chemistry*, vol 16 (2006) p. 286-291.
- 15 S. Sugiyama, T. Osaka, Y. Ueno, K-I Sotowa, Oxidative Dehydrogenation of Propane over Vanadate Catalysts Supported on Calcium and Strontium Hydroxyapatites, *Journal of the Japan Petroleum Institute*, vol 51 (2008) p. 50-57.
- 16 St. Naray-Szabo, *Zeitschrift für Kristallographie*, vol 75 (1930) p.387-398.
- 17 M. Mehmel, *Zeitschrift für Kristallographie*, vol 75 (1930) p. 323-331.
- 18 J.C. Elliott, R.M. Wilson and S.E.P. Dowker, JCPDS-International Centre for Diffraction Data 2002, *Advances in X-ray Analysis*, vol 45.
- 19 N.S. Resende, M. Nele, V.M.M. Salim, Effect of anion substitution on the acid properties of hydroxyapatite, *Thermochimica Acta*, vol 451 (2006) p. 16-21.
- 20 T. Kawasaki, S. Takahashi, K. Ikeda, Hydroxyapatite high-performance liquid chromatography: column performance for proteins, *European Journal of Biochemistry*, vol 152, (1985) p. 361-371.
- 21 K. Kandori, T. Shimizu, A. Yasukawa, T. Ishikawa, Adsorption of bovine serum albumin onto synthetic calcium hydroxyapatite: influence of particle texture, *Colloids and Surfaces B: Biointerfaces*, vol 5 (1995) p. 81-87.
- 22 A. Gervasini, A. Auroux, C. Guimon, Acidic Character of Metal-Loaded Amorphous and Crystalline Silica-Aluminas determined by XPS and Adsorption Calorimetry, *Journal of Physical Chemistry B*, vol 103 (1999) p. 7195-7205.
- 23 P. Carniti, A. Gervasini, S. Biella; Determination of Catalyst Surface Acidity in Liquids by a Pulse Liquid Chromatographic Technique; *Adsorption Science & Technology*, 23 (2005) p. 739-749.
- 24 C. Lamonier, J.-F. Lamonier, B. Aellach, A. Ezzamarty, J. Leglise, Specific tuning of acid/base sites in apatite materials to enhance their methanol thiolation catalytic performances, *Catalysis Today*, vol 164 (2011) p. 124-130.
- 25 J. Rodriguez-Carjaval, Recent Developments of the Program FULLPROF, in Commission on Powder Diffraction, *International Union of Crystallography (IUCr) Newsletter*, No. 26 (2001) p. 12-19.
- 26 P. Thomson, D.E. Cox, J.B. Hastings, Rietveld Refinement of Debye-Scherrer Synchrotron X-ray Data from Al<sub>2</sub>O<sub>3</sub>, *J. Appl. Cryst.* (1987), 20, p. 79-83.
- 27 S. Raynaud, E. Champion, D. Bernache-Assollant, P. Thomas, Calcium phosphate apatites with variable Ca/P atomic ratio I. Synthesis, characterization and thermal stability of powder, *Biomaterials*, vol 23 (2002) p. 1065-1072.
- 28 B. Aellach, A. Ezzamarty, J. Leglise, C. Lamonier, J.-F. Lamonier, Calcium-deficient and stoichiometric hydroxyapatites promoted by Cobalt for the catalytic removal of oxygenated Volatile Organic Compounds, *Catalysis Letters*, vol 135 (2010) p. 197-206.
- 29 J.M. Hughes, M. Cameron, K.D. Crowley, Structural variations in natural F, OH and Cl apatites, *American Mineralogist*, 74 (1989), p. 870-876.
- 30 M. Jarvinen, Application of symmetrized harmonics expansion to correction of the preferred orientation effect, *Journal of Applied Crystallography*, vol 26 (1993) p. 525-531.

- 31 J.F. Berar and P. Lelann, E.s.d.'s and estimated probable error obtained in Rietveld refinements with local correlations, *Journal of Applied Crystallography* vol 24, (1991) p. 1-5.
- 32 A. Krajewski, M. Mazzochi, P.L. Buldini, A. Ravaglioli, A. Tinti, P. Taddei and C. Fagnano, Synthesis of carbonated hydroxyapatites: efficiency of the substitution and critical evaluation of analytical methods, *Journal of Molecular Structure*, vol 744 (2005) p. 221-228.
- 33 R.M. Wilson, J.C. Elliott, S.E.P. Dowker, R.I. Smith, Rietveld structure refinement of precipitated carbonate apatite using neutron diffraction data, *Biomaterials*, vol 25 (2004) p. 2205-2213.
- 34 R.Z. Legeros, O.R. Trautz, J.P. Legeros, E. Klein, W.P. Shirra, Apatite Crystallites: Effects of Carbonate on Morphology, *Science*, vol 155 (1967) p. 1409-1411.
- 35 S. Kannan, J.M.G. Ventura, A.F. Lemos, A. Barba and J.M.F. Ferreira, Effect of sodium addition on the preparation of hydroxyapatites and biphasic ceramics, *Ceramics International*, vol 34 (2008) p. 7-13.
- 36 I.R. Gibson, I. Rehman, S.M. Best, W. Bonfield, Characterization of the transformation from calcium-deficient apatite to  $\beta$ -tricalcium phosphate, *Journal of Material Science : Materials in medicine*, vol 12 (2000) p. 799-804.
- 37 A. Yasukawa, K. Kandori, T. Ishikawa, TPD-TG-MS Study of Carbonate Calcium Hydroxyapatite Particles, *Calcified Tissue International*, vol 72 (2003) p. 243-250.
- 38 N. Elazarifi, A. Ezzamarty, J. Leglise, L.C. de Ménorval, C. Moreau, Kinetic study of the condensation of benzaldehyde with ethylcyanoacetate in the presence of Al-enriched fluoroapatites and hydroxyapatites as catalysts, *Applied Catalysis A: General*, vol 267 (2004) p. 235.
- 39 S. Kannan, I.A.F. Lemos, J.H.G. Rocha and J.M.F. Ferreira, Synthesis and characterization of magnesium substituted biphasic mixtures of controlled hydroxyapatite/ $\beta$ -tricalcium phosphate ratios, *Journal of Solid State Chemistry*, vol 178 (2005) p. 3190-3196.
- 40 M.E. Fleet and X. Liu, Coupled substitution of type A and B carbonate in sodium-bearing apatite, *Biomaterials*, vol 28 (2007) p. 916-926.
- 41 G. Bonel, Contribution a l'etude de la carbonatation des apatites. I.Synthese et etude des proprietes physico-chimiques des apatitescarbonatees du type A, *Annali di Chimica*, vol 7 (1972) p. 65-88.
- 42 J.C. Elliott, Space group and lattice constants of  $\text{Ca}_{10}(\text{PO}_4)_6\text{CO}_3$ , *Journal of Applied Crystallography*, vol 13 (1980) p. 618-621.
- 43 A. Krajewski, M. Mazzochi, P.L. Buldini, A. Ravaglioli, A. Tinti, P. Taddei and C. Fagnano, *Journal of Molecular Structure*, vol 744 (2005) p. 221-228.
- 44 Z.R. Hinedi, S. Goldberg, A.C. Chang, J.P. Yesinowski, A  $^{31}\text{P}$  and  $^1\text{H}$  MAS NMR study of phosphate sorption onto Calcium carbonate, *Journal of Colloid and Interface Science*, vol 152 (1992) p. 141-160.
- 45 C. Jager, T. Welzel, W. Meyer-Zaika, M. Epple, A solid-state NMR investigation of the structure of nanocrystalline hydroxyapatite, *Magnetic resonance in chemistry*, vol 44 (2006) p. 573-580.
- 46 S. Sugiyama, T. Miyamoto, H. Hayashi, J. B. Moffat, Effects of non-stoichiometry of calcium and strontium hydroxyapatites on the oxidation of ethane in the presence of tetrachloromethane, *Journal of Molecular Catalysis A Chemical*, vol 135 (1998) p. 199-208.
- 47 N.S. Resende, M. Nele, V.M.M. Salim, Effect of anion substitution on the acid properties of hydroxyapatite, *Thermochimica Acta*, vol 451 (2006) p. 16-21.
- 48 T. Kawasaki, S. Takahashi, K. Ikeda, Hydroxyapatite high-performance liquid chromatography: column performance for proteins, *European Journal of Biochemistry*, vol 152 (1985) p. 361-371.
- 49 S. Ogo, A. Onda, Y. Iwasa, K. Hara, A. Fukuoka, K. Yanagisawa, 1-Butanol synthesis from ethanol over strontium phosphate hydroxyapatite catalysts with various Sr/P ratios, *Journal of Catalysis*, vol 296 (2012) p. 24-30.
- 50 A. Gervasini, C. Messi, D. Flahaut, C. Guimon, Acid properties of iron oxide catalysts dispersed on silica-zirconia supports with different Zr content, *Applied Catalysis A: General*, 367 (2009) 113-121.
- 51 L. Silvester, J.-F. Lamonier, J. Faye, M. Capron, R.-N. Vannier, C. Lamonier, J.-L. Dubois, J.-L. Couturier, C. Calais, F. Dumeignil, to be submitted to *Green Chem.* (2014).

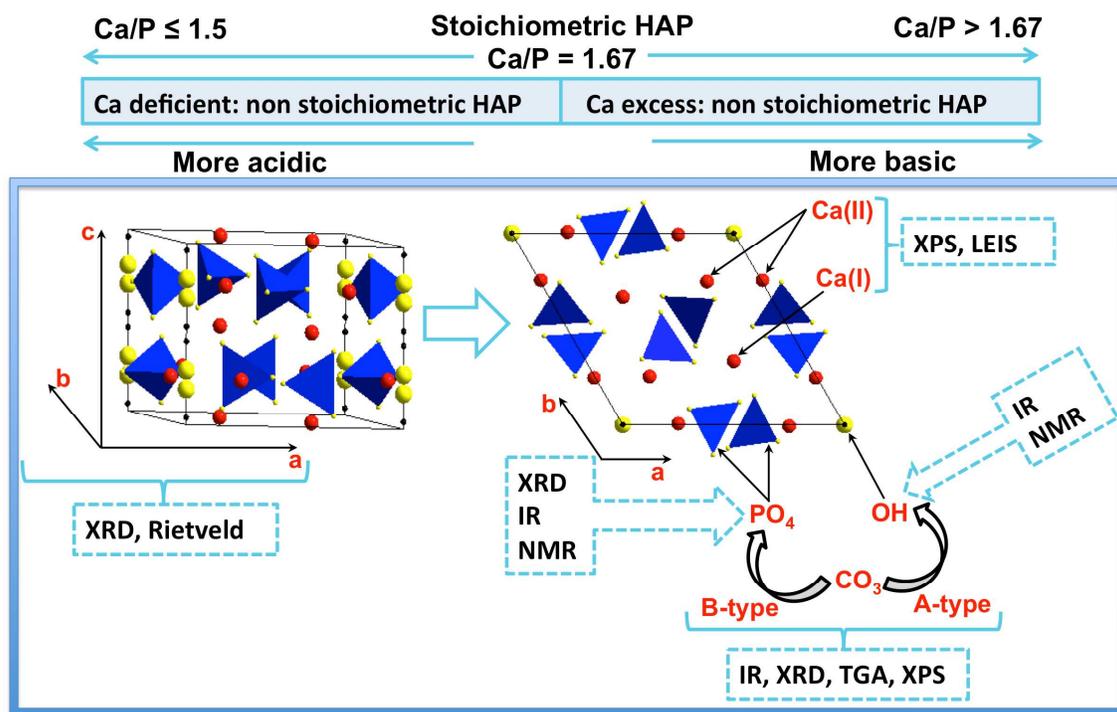

HAP solids were prepared by modifying their Ca/P ratio and by introducing Na<sup>+</sup> cations before being extensively characterized by XRD, XPS, LEIS, NMR, IR, TGA... Their acid base properties were then measured and discussed in relation with the characterization results.