

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

PAPER

Structural Discrimination of Double-Walled Carbon Nanotubes by Chiral Diporphyrin Nanocalipers

Gang Liu,^a Yukie Saito,^b Daisuke Nishio-Hamane,^c Ajoy K. Bauri,^d Emmanuel Flahaut,^e Tahahide Kimura^a and Naoki Komatsu^{*a}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX
DOI: 10.1039/b000000x

In this contribution, we demonstrate separation of double-walled carbon nanotubes (DWNTs) by host-guest methodology. New chiral diporphyrin nanocalipers with a longer spacer (~1.9 nm) consisting of carbazole-pyrene-carbazole are rationally designed as a host on the basis of the previous chiral diporphyrin nanocalipers with carbazole-anthracene-carbazole spacer (~1.4 nm). The chiral nanocalipers are found to recognize the diameter of DWNTs to make diameter distribution much narrower. In addition, the extracted carbon nanotubes (CNTs) exhibited circular dichroism (CD) after removal of the chiral nanocalipers and dissolution in water in the presence of achiral surfactant.

1. Introduction

Carbon nanotubes (CNTs) have been in the forefront of nanomaterial research in the past decades due to their unique physical and chemical properties. According to the number of layers, CNTs have been classified into the following three kinds: single-walled CNTs (SWNTs), double-walled CNTs (DWNTs), and multi-walled CNTs (MWNTs). While extensive fundamental studies and practical applications have been performed on SWNTs,¹⁻⁵ DWNTs have attracted increasing interest because of their superior properties including both characteristics of SWNTs and MWNTs.⁶⁻¹⁰

Since the properties of CNTs are known to correlate with their structures,¹ the structural uniformity of CNTs in terms of number of walls, diameter, length, roll-up index or (*n*, *m*), and/or handedness is preferable for fine applications. Although various methods for targeting separation and selective synthesis have been developed for SWNTs,¹¹⁻¹³ DWNTs are left behind far from SWNTs in spite of their utility. The direct synthesis of DWNTs¹⁴ results in significant quantity of SWNTs and MWNTs accompanied with DWNTs and broad diameter distribution of DWNTs.¹⁵⁻¹⁸ The separation of DWNTs has been limited to density gradient ultracentrifugation (DGU) method¹⁹⁻²⁴ except for the methods using chromatography²⁵ and biopolymers.^{26, 27} Despite the superior properties of DWNTs, the separation of DWNTs has been rarely reported probably because of the wider range of diameters and number of walls included in the as-synthesized DWNTs. In addition, optically active DWNTs have not been reported yet, though many optically active SWNTs have been identified.^{11, 12} This motivates us to design chiral diporphyrin nanocalipers to discriminate the handedness of DWNTs.

Herein, we report on the separation of DWNTs through molecular recognition by chiral diporphyrin nanocalipers with a

larger cavity than the previous ones applied to the separation of SWNTs.²⁸ Since an advantage of our host-guest methodology for CNT separation lies in the flexibility in molecular design of the host for targeting CNTs, we rationally designed a wider nanocalipers with carbazole-pyrene-carbazole spacer having 1.9 nm in length for DWNT separation as shown in Scheme 1.


2 Results

2.1 Synthesis of the chiral diporphyrin nanocalipers

The chiral diporphyrin nanocalipers are synthesized through Suzuki-Miyaura coupling reaction as shown in Scheme 1. The long spacer consisting of three aromatic units (carbazole-pyrene-carbazole) was directly prepared by coupling the commercial pyrene-2,7-diboronate with 3-bromo-9-octyl-9*H*-carbazole in 62% yield. After bromination, the resulting bromide was allowed to react with two chiral porphyrins through Suzuki-Miyaura coupling reaction to give (*R*)- or (*S*)-**1**, respectively, in ~40% yield. The products were fully identified by absorption, circular dichroism (CD), ESI-MS, and ¹H and ¹³C NMR spectroscopies (Fig. 1 and ESI).

2.2. Extraction of DWNTs with chiral diporphyrin nanocalipers

DWNTs used in this work were prepared by catalytic chemical vapor deposition (CCVD) as reported previously.¹⁴ According to the literature, high-resolution transmission electron microscopy (HR-TEM) showed that as-prepared sample consists of 77% DWNTs, 18% SWNTs, and 5% triple-walled CNTs (TWNTs). The diameter of DWNTs ranged from 1.23 nm to 3.23 nm for outer tubes and from 0.53 nm to 2.53 nm for inner tubes (Fig. 4).¹⁴ In the extraction, DWNTs and chiral nanocalipers (*R*)- or (*S*)-**1** in methanol were bath-sonicated and centrifuged for two days (see Experimental section in detail). The resulting greenish extract was quite stable without sedimentation even after four

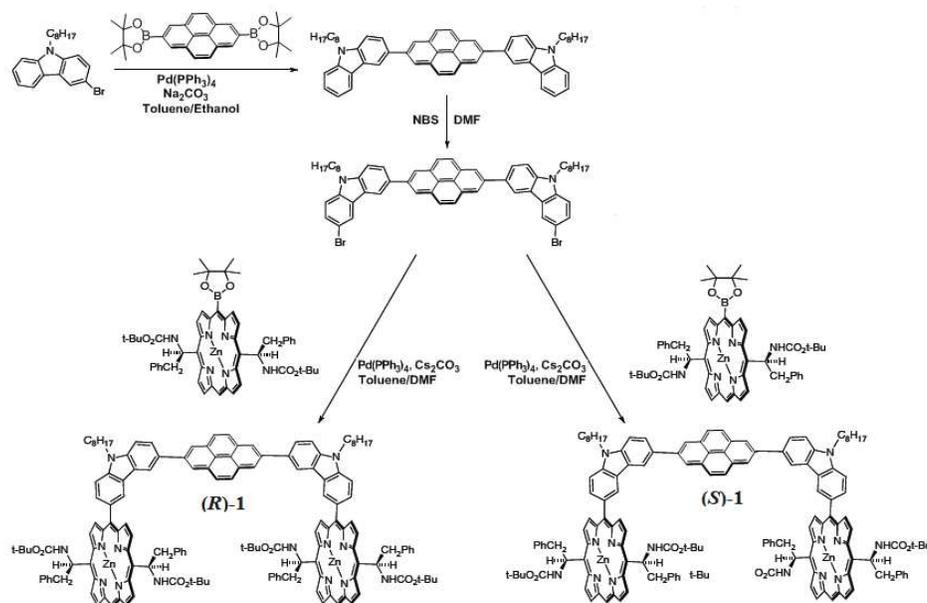

Scheme 1 Synthesis of chiral diporphyrin nanocalipers (*R*)- and (*S*)-1.

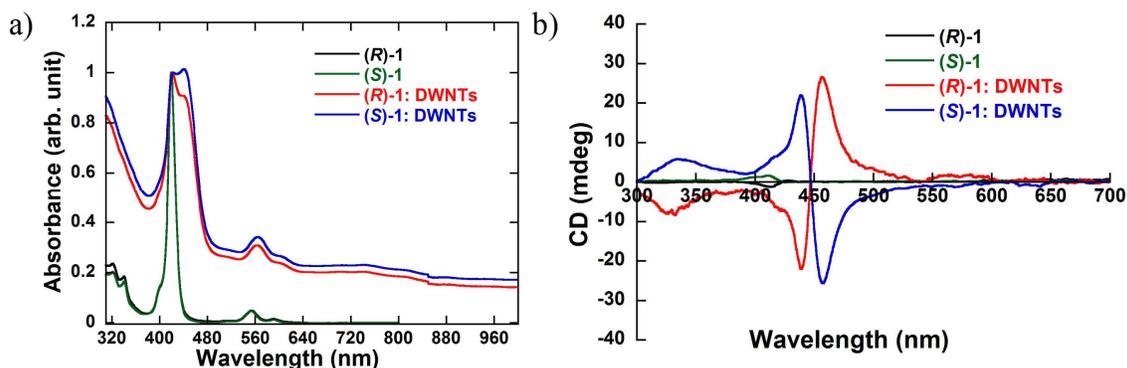


Fig. 1 Absorption (a) and CD spectra (b) of (*R*)- and (*S*)-1 before and after extraction. CD spectra of nanocalipers and nanocaliper-DWNT complexes were normalized at the absorbance of 419 nm and 440 nm, respectively.

months. The extract was then subjected to UV-vis-NIR, CD, and fluorescence spectroscopy measurements to confirm the existence of the complex between DWNTs and **1**.

In the absorption spectra shown in Fig. 1a, the Q bands of the porphyrins in the nanocalipers **1** are broadened and red-shifted from 554 nm to 565 nm upon complexation with DWNTs. In addition, a new peak appears at 441 nm, which may be caused by the red shift of the Soret band. These spectral changes may be attributed to the $\pi - \pi$ and/or C-H $-\pi$ interactions between the nanocalipers and CNTs.²⁹ The upward shift of the baseline and broad peak from 700 nm to 900 nm indicate that a significant amount of CNTs was extracted into the solution phase and present as stable complexes with nanocalipers in the extract. The complexation of CNTs and **1** is further confirmed by the quenching of fluorescence from the porphyrins (Fig. S1) and the enhanced Cotton effects in CD spectra (Fig. 1b) due to the fixation of the two chiral porphyrins.³⁰

As shown in the scanning electron microscopy (SEM) and scanning transmission electron microscopy (STEM) images (Fig. 2), almost all the strings are individualized without bundling in the whole region we scanned, indicating the high stability of the

CNT complex with **1**. Direct evidence of the complexation between nanocalipers and DWNT is given by the HR-TEM images, which will be discussed below.

2.3. Diameter distribution of DWNTs before and after the extraction

In order to evaluate the recognition ability of the nanocalipers **1** towards the CNT structure, we measured HR-TEM of the extract, Raman spectra after washing out the nanocalipers from the extracted CNT complexes, and absorption and CD spectra after dissolving the washed sample in D₂O (see Experimental section in detail). In the absorption spectra, the observed bands are not so sharp as those of SWNTs used in our previous studies,^{28, 31, 32} probably because the large abundance of DWNTs significantly increases the variety in the tubular carbon structures. Since the absorption spectra is concluded to have little valuable information for structural determination of CNTs before and after the extraction, the spectra are shown in ESI (Fig. S4) along with the possible interpretation based on the Kataura plot.¹

2.3.1. HR-TEM analysis of the extract

For determination of the enriched diameter range through the extraction, we measured HR-TEM of the extract with **1**. Three

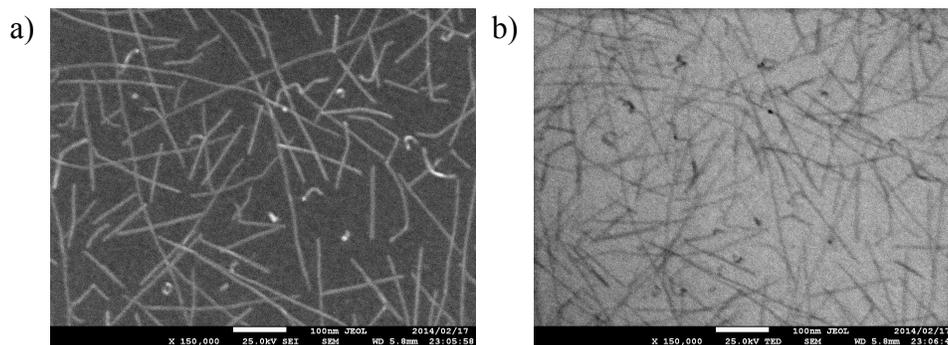


Fig. 2 SEM (a) and STEM (b) images of the CNT complexes with **1**. Two images were taken at the same region.

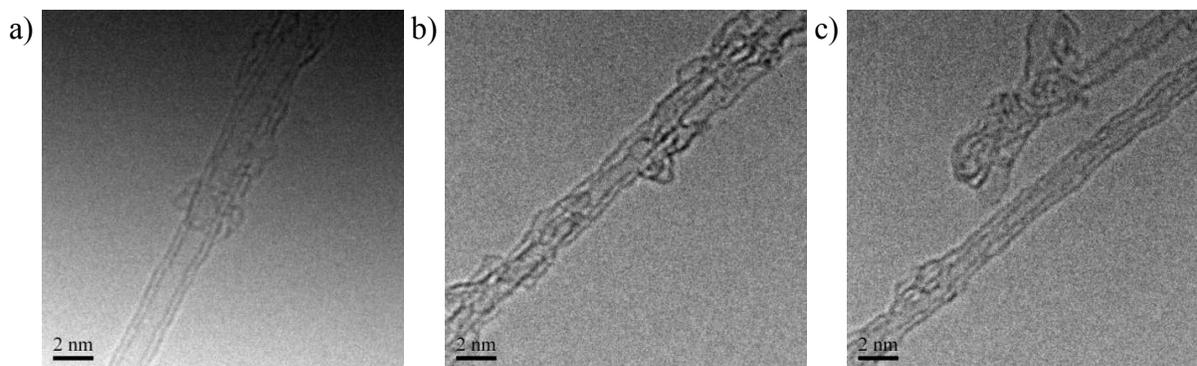


Fig. 3 Typical HR-TEM images of DWNTs wrapped with nanocalipers **1**. The respective outer and inner diameters are (a) 1.71 and 1.02 nm, (b) 1.58 and 0.91 nm, and (c) 1.47 and 0.76 nm.

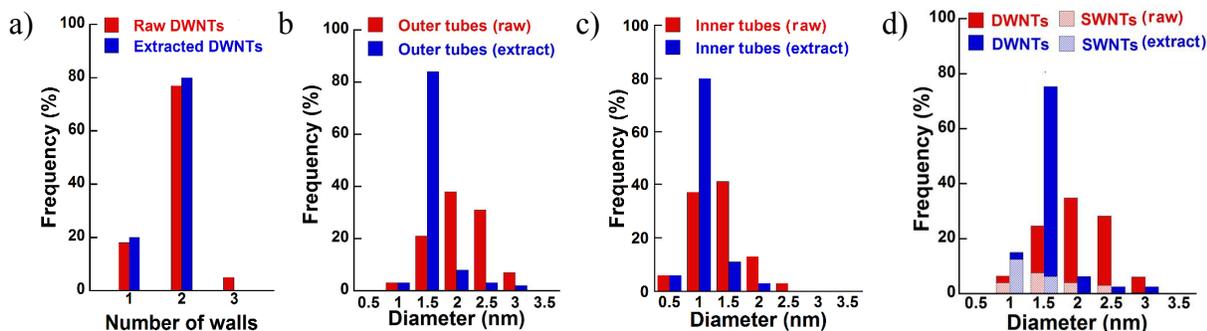


Fig. 4 Frequency of SWNTs, DWNTs, and TWNTs (a), diameter distribution of outer (b) and inner (c) tubes in DWNTs, and CNTs (SWNTs + DWNTs) (d) before and after the extraction with (*R*)-**1**. The distribution in number of walls and in diameter of raw sample is adapted from ref. 14.

typical images of the extracted DWNTs are shown in Fig. 3. In these images, the CNTs are wrapped with some materials, which are considered to be the nanocalipers as in the case of SWNTs.²⁸ In addition, two walls are discriminated clearly enough to measure the diameters of the inner and outer tubes in these DWNTs. The analysis of 81 isolated CNTs allowed us to determine the distribution in the number of walls, and the diameters of the inner and outer tubes (Fig. 4).

Although SWNTs are found in the images, TWNTs included at 5% before the extraction disappear after the extraction, implying that nanocalipers **1** cannot form the stable complex with TWNTs

because of their large diameters. The distribution of the number of walls before and after the extraction is shown in Fig. 4a. The abundance of SWNTs and DWNTs slightly increases from 18% and 77% to 20% and 80%, respectively, because TWNTs are not extracted as mentioned above. This phenomenon implies that the nanocalipers cannot discriminate SWNTs and DWNTs, and may recognize diameters of the CNTs. Therefore, the ratio between the SWNTs and DWNTs after the separation should be influenced by that before the separation.

In terms of diameter selectivity, remarkable diameter shift through the extraction is indicated by the histogram shown in Fig.

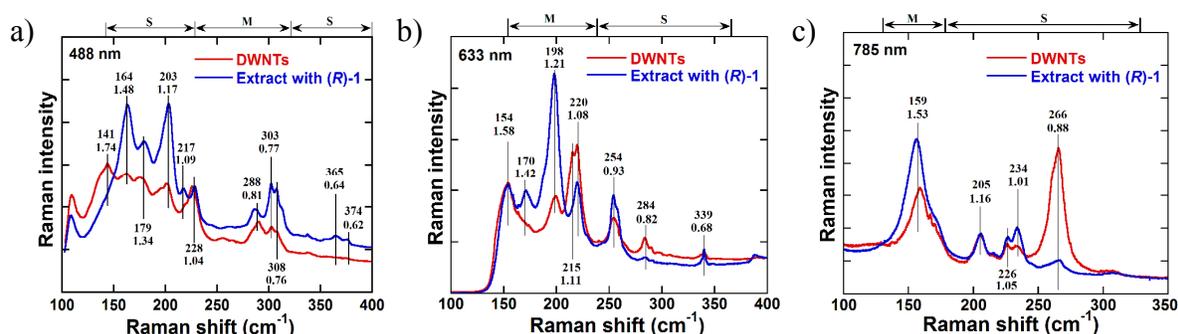


Fig. 5 Raman spectra of DWNTs before and after the extraction with (R)-1 in the RBM. Wave number (cm^{-1}) and the corresponding diameter (nm) are indicated at each peak. S and M at the top of the spectra indicate semiconducting and metallic, respectively.

4b – 4d. DWNTs with 1.25 – 2.75 nm in outer tube diameters are the major components (90%) in the raw DWNTs as indicated in Fig. 4b. After the extraction, DWNTs with much narrower diameter range, 1.25 – 1.75 nm, increase from 21% to 84%. DWNTs with the diameter of $1.50 \text{ nm} \pm 0.25 \text{ nm}$ are concluded to be highly enriched through the extraction due to the preference of the nanocalipers **1** to the diameter range, as we intended through rational design of the host molecule.

Since 20% of the CNTs found in the HR-TEM images are SWNTs, their diameter range is also compared before and after the extraction. As shown in Fig. 4d and S2, diameter range of the SWNTs became much narrower from 0.75 – 2.75 nm to 0.75 – 1.75 nm through the extraction as in the case of the outer tube mentioned above. The histogram of the SWNT diameters with narrower steps (0.2 nm) shown in Fig. S3a indicates that the diameter range of $1.10 \text{ nm} \pm 0.10 \text{ nm}$ is highly enriched after the extraction. The broad diameter range of SWNTs before the extraction is made to be much narrower and be shifted to relatively small diameter through the extraction.

Since the nanocalipers **1** is considered to recognize the diameters of not only the outer tubes of DWNTs but also SWNTs, the diameter distribution of CNTs irrespective of number of layers is compared as shown in Fig. 4d and S3b. Although most of the extracted DWNTs are in the range of $1.50 \text{ nm} \pm 0.25 \text{ nm}$ in the diameters as shown in Fig. 4b, CNTs with 0.75 – 1.75 nm in Fig. 4d, or 1.0 – 1.8 nm in Fig. S3b, are enriched in the extracted CNTs (SWNTs + DWNTs).

2.3.2. Raman analysis of the extract

After the methanol extracts of DWNTs with (R)- and (S)-**1** were concentrated, the resulting black solids were washed with THF and pyridine several times to thoroughly remove the nanocalipers from the complex. More than 70% of the chiral nanocalipers were recovered and reused after purification. The washed samples were subjected to Raman spectroscopy at the excitation of 488, 633, and 785 nm to determine the diameter range enriched through the extraction. Since the DWNTs extracted with (R)- and (S)-**1** exhibited almost the same spectra, the spectra before and after the extraction with (R)-**1** are shown in Fig. 5 and the results are summarized in Table 1. The diameter of CNTs is calculated by the following equation (1);

$$\omega_{\text{RBM}} = 223.5/d + 12.5 \quad (1)$$

where ω_{RBM} is the Raman shift (cm^{-1}) of the radial breathing mode (RBM) and d is the diameter (nm) of CNTs.³³

At the excitation of 488 nm, prominent spectral change is observed in the lower frequency region through the extraction with nanocalipers **1**. As shown in Fig. 5a, the peaks in the region of 164 – 217 cm^{-1} corresponding to the diameters of 1.09 – 1.48 nm are significantly enriched through the extraction. Adjacent peaks at 141 and 228 cm^{-1} corresponding to the diameters of 1.74 and 1.04 nm, respectively, decrease in the intensity, or relative abundance. Although most of the peaks increase in the higher frequency region, they are assigned to be the inner tubes in the DWNTs because of their diameters smaller than 0.8 nm. Similar phenomena are observed in the spectra excited at 633 and 785 nm (Fig. 5b and 5c, respectively). The drastic increase in the intensity is observed in the peaks at 170 and 198 cm^{-1} corresponding to 1.42 and 1.21 nm, respectively, at 633 nm excitation, and at 159 cm^{-1} corresponding to 1.53 nm at 785 nm excitation. The reduction in the peak intensity is detected at 215 and 220 cm^{-1} (1.11 and 1.08 nm, respectively) at 633 nm excitation and at 266 cm^{-1} (0.88 nm) at 785 nm excitation.

From the summary of the results in the Raman analyses shown in Table 1, we can conclude that the diameter range of 1.1 – 1.5 nm is enriched through the extraction with nanocalipers **1**. The enriched diameter range determined by HR-TEM as mentioned above (Fig. S3b) is 1.0 – 1.8 nm, which will be narrowed by applying the results of the Raman analysis (Table 1). At the small diameter region, the border between increase and decrease is distinct at 1.1 nm shown in Table 1, reducing the above diameter

Table 1 Comparison in the Raman intensity of CNTs before and after extraction^a

Excitation wavelength / nm	488	633	785
Increased diameters / nm ^b	1.09 – 1.48 (S)	1.20 (M), 1.42 (M)	1.53 (M)
Decreased diameters / nm ^c	1.04 (M), 1.74	1.10 (M), 1.08 (M)	0.88 (S)

^a M and S in parentheses denote metallic and semiconducting, respectively. ^b Diameters or diameter range of CNTs increased in their Raman intensity. ^c Diameters of CNTs decreased in their Raman intensity.

range from 1.0 – 1.8 nm to 1.1 – 1.8 nm. At the large diameter region, CNTs with 1.7 nm decrease their relative abundance shown in Table 1. Because of lack in Raman information between 1.5 – 1.7 nm in diameter, the enriched diameter range is concluded to be 1.1 – 1.7 nm, taking into consideration both of the results in the HR-TEM and Raman measurements.

2.4. Optical enrichment of extracted CNTs

The optical enrichment of the extracted CNTs is confirmed by CD spectra of the SDBS-D₂O dispersion of the washed CNTs after the extraction, as shown in Fig. 6. The CNTs extracted with (R)- and (S)-1 exhibit almost symmetrical CD, indicating that the extracted CNTs are optically active.

Clear CDs are observed at the regions of 550 – 600 nm, 600 – 680 nm, and 680 – 770 nm, which are corresponding to the diameter ranges of the extracted CNTs shown in Table 2, based on the Kataura plot.¹ Although much smaller number of CNTs are theoretically possible to exhibit higher intensity of CD than much more abundant CNTs, we would like to assume that the CD intensity is proportional to the abundance of the optically active CNTs to interpret the result of the CD.

For the CDs in the range of 550 – 600 nm (Table 2), semiconducting outer tubes with 1.4 – 1.6 nm are considered to be more responsible than semiconducting inner tubes with ~0.7 nm and metallic SWNTs with 1.0 – 1.2 nm because of their abundance shown in Fig. 4c and 4d. In the range of 600 – 680 nm, the inner tubes with 0.7 – 0.9 nm, SWNTs with 1.1 – 1.3 nm, and the outer tubes with 1.5 – 1.8 nm are included in their most abundant regions of the inner tube (0.75 – 1.25 nm, Fig. 4c), SWNTs (1.0 – 1.2 nm, Fig. S3a), and outer tube (1.25 – 1.75 nm, Fig. 4b), respectively. However, the metallic SWNTs with 1.1 – 1.3 nm should be less responsible to the CD in the region because of the much less abundance of SWNTs than DWNTs shown in Fig. 4a and metallic tubes than semiconducting ones theoretically. Since the chiral diporphyrin nanocalipers can recognize the helical structures of the outer tubes in DWNTs, the CD in the region of 600 – 680 nm may be originated mostly from the outer tubes with 1.5 – 1.8 nm. If the helicity of the inner tubes has some influence from that of the outer tubes upon the DWNT synthesis, optically active inner tubes may happen indirectly through the optical resolution of the outer tubes.

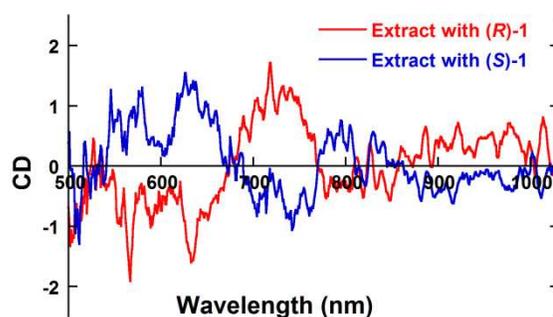


Fig. 6 CD spectra of DWNTs extracted with (R)- and (S)-1.

In the range of 680 – 770 nm, inner tubes with 0.8 – 1.0 nm and outer tubes with 1.3 – 1.5 nm are still in the abundant diameter regions indicated in the Fig. 4c and 4b, respectively, though outer tubes above the 1.8 nm diameter are out of the range (Fig. 4b). Therefore, the CD in the region of 680 – 770 nm can be attributed to the semiconducting inner tubes with 0.8 – 1.0 nm and/or the metallic outer tubes with 1.3 – 1.5 nm. If the aforementioned helical correlation between the outer and inner tubes is not so strong in DWNTs, the metallic outer tubes with 1.3 – 1.5 nm are concluded to contribute mainly to the CD in the region of 680 – 770 nm. Due to much more abundance of DWNTs than that of SWNTs (Fig. 4a), the metallic outer tubes with 1.3 – 1.5 nm are considered to exhibit CD in much higher intensity than the metallic SWNTs with 1.1 – 1.3 nm mentioned above.

From the above discussion based on the CD (Fig. 6 and Table 2), we can conclude that the optically active forms of DWNTs are most probably obtained through molecular recognition with chiral diporphyrin nanocalipers.

3 Discussion

In order to understand the diameter preference of nanocalipers 1 toward CNTs, we carried out molecular modeling calculations (molecular mechanics) for the 1:1 complex between (R)-1 and a SWNT with diameter of 1.0 nm (Fig. 7a), and DWNTs with outer tube diameters of 1.5 and 2.0 nm (Fig. 7b and 7c, respectively).

Table 2 Diameter range of CNTs responsible to the CD

Range / nm in CD observation	Corresponding energy range / eV	Corresponding diameter range / nm (optical transition) ^a	Assignment
550 – 600	2.1 – 2.3	~0.7 (E_{22}^S)	inner tube
		1.0 – 1.2 (E_{22}^M)	SWNT
		1.4 – 1.6 (E_{33}^S)	outer tube
600 – 680	1.8 – 2.1	0.7 – 0.9 (E_{22}^S)	inner tube
		1.1 – 1.3 (E_{22}^M)	SWNT
		1.5 – 1.8 (E_{33}^S)	outer tube
680 – 770	1.6 – 1.8	0.8 – 1.0 (E_{22}^S)	inner tube
		1.3 – 1.5 (E_{22}^M)	outer tube
		>1.8 (E_{33}^S)	outer tube

^a The italic diameter range indicates that the tubes in the range may contribute to the CD more than those in the other ranges.

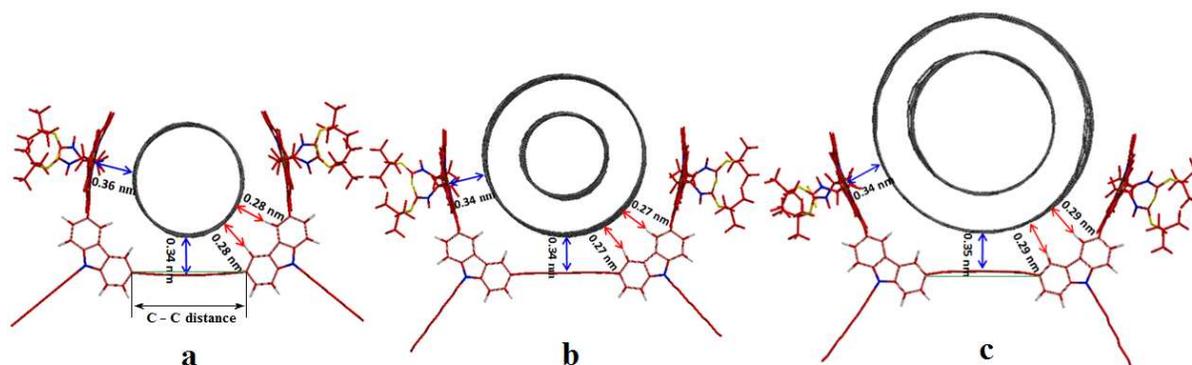


Fig. 7 Computer-generated molecular modeling of the complex structures of chiral diporphyrin nanocalipers **1** with SWNT with a diameter of 1.0 nm (a), and DWNTs with outer tube diameter of 1.5 nm (b) and 2.0 nm (c). Blue and red arrows indicate $\pi - \pi$ and C-H - π interactions, respectively. C - C distance indicated in (a) is compared with those in (b) and (c) in Table 3.

The energy-minimized structures shown in Fig. 7 indicate that nanocalipers **1** is somewhat flexible to accept different diameters of CNTs. In all the complex structures, there are $\pi - \pi$ interactions between CNT surface and porphyrin or pyrene to stabilize the complexes, as indicated by blue arrows in Fig. 7. In addition, C-H - π interactions between carbazole in the spacer and CNT surface improve the stability in the complexes (red arrows in Fig. 7). Although the same numbers of these interactions exist in all the complexes of **1** with CNTs, the shape of the host molecule in these complexes and the distances in these interactions are not exactly the same, resulting in the difference in the complex stability.

For the SWNT with diameter of 1.0 nm, the corresponding complex shown in Fig. 7a is considered to be less stable, because the pyrene moiety and the adjacent single bonds are bent significantly to accommodate the SWNT with much smaller diameter than the cavity size. The degree in the deformation of the nanocalipers is quantified by the dihedral angle between the two porphyrins and the distance between the two carbon atoms bound to the pyrene moiety as shown in Fig. 7a (Table 1). In this case, the dihedral angle is made to be 26° and the C - C distance becomes 9.97 Å. The bending of the pyrene moiety, shortening the C - C distance, makes the dihedral angle between two porphyrins larger and the cavity smaller to accommodate the small diameter SWNT.

Significant deformation of the nanocalipers **1** is also observed in the case of DWNT with outer tube diameter of 2.0 nm (Fig. 7c). In contrast to Fig. 7a, the cavity of the nanocalipers is made to be open to accept the DWNT with 2.0 nm in diameter as shown in Fig. 7c. The degree of the deformation is larger in Fig. 7c than that in Fig. 7a; that is, the dihedral angle and C - C distance become 42° and 9.96 Å, respectively (Table 3).

On the other hand, the host molecule accommodates DWNT

Table 3 The dihedral angle of the two porphyrins and the C - C distance indicated in Fig. 7a

Diameter of SWNT / nm	1.0	1.5	2.0
Dihedral angle / $^\circ$	26	10	42
C - C distance / Å	9.97	9.99	9.96

with 1.5 nm without any distinct strain as shown in Fig. 7b. The two porphyrins are nearly in parallel with the dihedral angle of only 10° and the pyrene is flat with longer C - C distance of 9.99 Å. The order in the degree of deformation in these complexes estimated from Table 3, DWNT (2.0 nm) / **1** > SWNT (1.0 nm) / **1** >> DWNT (1.5 nm) / **1**, correlates with that in the abundance of CNTs after the extraction as shown in Fig. 4d. This indicates that the diameters of CNTs are discriminated on the basis of the stability of the complex. In addition, left- and right-handed (*M*- and *P*-) structures^{12, 34} of the DWNTs may be discriminated by the difference in the stability between the diastereomers; (*R*)-**1** / (*M*)-DWNT and (*R*)-**1** / (*P*)-DWNT, and (*S*)-**1** / (*M*)-DWNT and (*S*)-**1** / (*P*)-DWNT.

4 Conclusions

Based on the previous research on the separation of SWNTs with chiral diporphyrins, we rationally designed and synthesized a new chiral diporphyrin nanocalipers with a much longer spacer consisting of carbazole-pyrene-carbazole (~1.9 nm) for the separation of DWNTs. As we designed, the chiral nanocalipers are found to discriminate the diameter of DWNTs; DWNTs with 1.25 - 1.75 nm in diameter are highly enriched through the extraction with the chiral diporphyrin nanocalipers. CD is also observed in the extracted CNTs. The diameters of the experimentally increased and decreased CNTs correlate with the degree of deformation, or stability, of the complexes on the basis of the computer generated complex structures.

5 Experimental section

Extraction of DWNTs with Nanocalipers: Chiral nanocalipers (*R*)- or (*S*)-**1** (10 mg) and DWNTs (10 mg) in methanol (40 mL) were bath-sonicated at 20 °C for 36 h. After centrifugation of the resulting suspension at 50 400 g for 45 h, the supernatant was poured up for UV-vis-NIR, fluorescence, CD, HR-TEM, SEM, and STEM measurements. After concentration of the supernatant, the residual solid was washed with THF and pyridine several times until the porphyrin Soret band disappeared in the UV-vis spectra of the washings. The thoroughly washed DWNTs (0.3 mg) were analyzed with Raman spectroscopy at excitation of 488,

633, and 785 nm. The solid sample was dispersed in D₂O (10 mL) in the presence of SDBS (10 mg/mL) by tip-sonication in rosette cooling cell³⁵ for 1.5 h at 0 °C. After centrifugation at 136 000 g for 40 min, the upper layer (about 85%) of the supernatant was poured up and subjected to UV-vis-NIR and CD measurements. For the dispersion of the raw DWNTs, tip-sonication was carried out for 40 min under the same conditions followed by centrifugation at 543 000 g for 30 min.

Acknowledgements

The authors thank Prof. Yasushi Kawai (Nagahama Institute of Bio-Science and Technology) for allowing us to use CD spectropolarimeter, Mr. Haruo Hosoda (Bruker Daltonics k.k.) for analyzing **1** with ESI-MS (micrOTOFII) spectroscopy. HR-TEM was performed using facilities of the Institute for Solid State Physics, the University of Tokyo. This work was financially supported by Grant-in-Aid for Scientific Research (S) (No. 24221009), Grant-in-Aid for Scientific Research on Priority Areas (No. 22016005), Grant-in-Aid for Scientific Research (B) (No. 23350062), the Kurata Memorial Hitachi Science and Technology Foundation, and Adaptable and Seamless Technology Transfer Program through Target-driven R&D (JST). G. L. acknowledges Japan Society for the Promotion of Science (JSPS) for providing him with a postdoctoral fellowship (ID No P13339).

Notes and references

^a Department of Chemistry, Shiga University of Medical Science, Seta, Otsu 520-2192, Japan. Fax: 81-77-548-2405; Tel: 81-77-548-2102; E-mail: nkomatsu@belle.shiga-med.ac.jp

^b Graduate School of Agricultural and Life Sciences, The University of Tokyo, 1-1-1 Yayoi, Bunkyo-ku, Tokyo, 113-8657, Japan

^c The Institute for Solid State Physics, The University of Tokyo, 5-1-5 Kashiwanoha, Kashiwa, Chiba, 277-8581, Japan

^d Bio-Organic Division, Bhabha Atomic Research Center, Trombay, Mumbai, 400085, India

^e Université de Toulouse; UPS, INP, CNRS; Institut Carnot Cirimat; 118, route de Narbonne, F-31062 Toulouse cedex 9, France.


† Electronic Supplementary Information (ESI) available: Fluorescence spectra of the complex (Fig. S1), diameter distribution of SWNTs (Fig. S2 and S3), absorption spectra of the extracted CNTs (Fig. S4), synthetic procedure, ¹H and ¹³C NMR and ESI-MS spectra of nanocalipers. See DOI: 10.1039/b000000x/

- H. Kataura, Y. Kumazawa, Y. Maniwa, I. Umezu, S. Suzuki, Y. Ohtsuka and Y. Achiba, *Synth. Metals*, 1999, **103**, 2555.
- M. Ouyang, J.-L. Huang and C. M. Lieber, *Acc. Chem. Res.*, 2002, **35**, 1018.
- J. M. Schnorr and T. M. Swager, *Chem. Mater.*, 2011, **23**, 646.
- A. D. Franklin, *Nature*, 2013, **498**, 443.
- R. H. Baughman, A. A. Zakhidov and W. A. d. Heer, *Science*, 2002, **297**, 787.
- K. Tanaka, H. Aoki, H. Ago, T. Yamabe and K. Okahara, *Carbon*, 1997, **35**, 121.
- H. Kurachi, S. Uemura, J. Yotani, T. Nagasako, H. Yamada, T. Ezaki, T. Maesoba, R. Loutfy, A. Moravsky, T. Nakazawa, S. Katagiri and Y. Saito, *IDW Proc.*, 2001, 1237.
- Y. A. Kim, H. Muramatsu, T. Hayashi, M. Endo, M. Terrones and M. S. Dresselhaus, *Chem. Phys. Lett.*, 2004, **398**, 87.

- T. Natsuki, T. Hayashi and M. Endo, *Appl. Phys. A*, 2006, **83**, 13.
- M. Endo, H. Muramatsu, T. Hayashi, Y. A. Kim, M. Terrones and M. S. Dresselhaus, *Nature*, 2005, **433**, 476.
- N. Komatsu and F. Wang, *Materials*, 2010, **3**, 3818.
- G. Liu, F. Wang, X. Peng, A. F. M. M. Rahman, A. K. Bauri and N. Komatsu, in *Handbook of carbon nano materials*, eds. F. D'Souza and K. M. Kadish, World Scientific, 2012, pp. 203.
- J. R. Sanchez-Valencia, T. Dienel, O. Groening, I. Shorubalko, A. Mueller, M. Jansen, K. Amsharov, P. Ruffieux and R. Fasel, *Nature*, 2014, **512**, 61.
- E. Flahaut, R. Bacsa, A. Peigney and C. Laurent, *Chem. Commun.*, 2003, 1442.
- H. Qi, C. Qian and J. Liu, *Nano Lett.*, 2007, **7**, 2417.
- E. Flahaut, A. Peigney, C. Laurent and A. Rousset, *J. Mater. Chem.*, 2000, **10**, 249.
- T. Yamada, T. Namai, K. Hata, D. N. Futaba, K. Mizuno, J. Fan, M. Yudasaka, M. Yumura and S. Iijima, *Nat Nano*, 2006, **1**, 131.
- T. Sugai, H. Yoshida, T. Shimada, T. Okazaki and H. Shinohara, *Nano Lett.*, 2003, **3**, 769.
- S. Yang, A. N. Parks, S. A. Saba, P. L. Ferguson and J. Liu, *Nano Lett.*, 2011, **11**, 4405.
- A. A. Green and M. C. Hersam, *Nat. Nanotechnol.*, 2009, **4**, 64.
- A. A. Green and M. C. Hersam, *ACS Nano*, 2011, **5**, 1459.
- J. Y. Huh, A. R. H. Walker, H. W. Ro, J. Obrzut, E. Mansfield, R. Geiss and J. A. Fagan, *J. Phys. Chem. C*, 2010, **114**, 11343.
- D. A. Tsyboulski, Y. Hou, N. Fakhri, S. Ghosh, R. Zhang, S. M. Bachilo, M. Pasquali, L.-C. Chen, J. Liu and R. B. Weisman, *Nano Lett.*, 2009, **9**, 3282.
- R. Fleurier, J.-S. Lauret, E. Flahaut and A. Loiseau, *Phys. Stat. Sol. (b)*, 2009, **246**, 2675.
- K. E. Moore, M. Pfohl, F. Hennrich, V. S. K. Chakradhanula, C. Kuebel, M. M. Kappes, J. G. Shapter, R. Krupke and B. S. Flavel, *ACS Nano*, 2014, **8**, 6756.
- H. Nie, H. Wang, A. Cao, Z. Shi, S.-T. Yang, Y. Yuan and Y. Liu, *Nanoscale*, 2011, **3**, 970.
- J. H. Kim, M. Kataoka, Y. A. Kim, D. Shimamoto, H. Muramatsu, T. Hayashi, M. Endo, M. Terrones and M. S. Dresselhaus, *Appl. Phys. Lett.*, 2008, **93**, 223107.
- G. Liu, F. Wang, S. Chaunchaiyakul, Y. Saito, A. Bauri, T. Kimura, Y. Kuwahara and N. Komatsu, *J. Am. Chem. Soc.*, 2013, **135**, 4805.
- G. Liu, A. F. M. M. Rahman, S. Chaunchaiyakul, T. Kimura, Y. Kuwahara and N. Komatsu, *Chem. Eur. J.*, 2013, **19**, 16221.
- V. V. Borovkov, G. A. Hembury and Y. Inoue, *Acc. Chem. Res.*, 2004, **37**, 449.
- F. Wang, K. Matsuda, A. F. M. M. Rahman, T. Kimura and N. Komatsu, *Nanoscale*, 2011, **3**, 4117.
- X. Peng, N. Komatsu, S. Bhattacharya, T. Shimawaki, S. Aonuma, T. Kimura and A. Osuka, *Nat. Nanotechnol.*, 2007, **2**, 361.
- S. M. Bachilo, M. S. Strano, C. Kittrell, R. H. Hauge, R. E. Smalley and R. B. Weisman, *Science*, 2002, **298**, 2361.
- X. Peng, F. Wang, A. K. Bauri, A. F. M. M. Rahman and N. Komatsu, *Chem. Lett.*, 2010, **39**, 1022.
- T. Yasumitsu, G. Liu, J.-M. Leveque, S. Aonuma, L. Duclaux, T. Kimura and N. Komatsu, *Ultrason. Sonochem.*, 2013, **20**, 37.

Structural Discrimination of Double-Walled Carbon Nanotubes by Chiral Diporphyrin Nanocalipers

Gang Liu, Yukie Saito, Daisuke Nishio-Hamane, Ajoy K. Bauri, Emmanuel Flahaut, Tahahide Kimura and Naoki Komatsu*

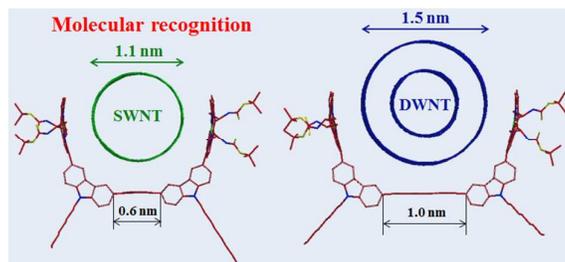

The spacer (carbazole-pyrene-carbazole) is made to be longer by 0.4 nm than that of the previous nanocalipers (carbazole-anthracene-carbazole), enabling DWNT separation. After the extraction, diameter distribution of DWNTs becomes much narrower from 1.25 – 2.75 nm to 1.25 – 1.75 nm.