


Journal of Materials Chemistry B

Accepted Manuscript

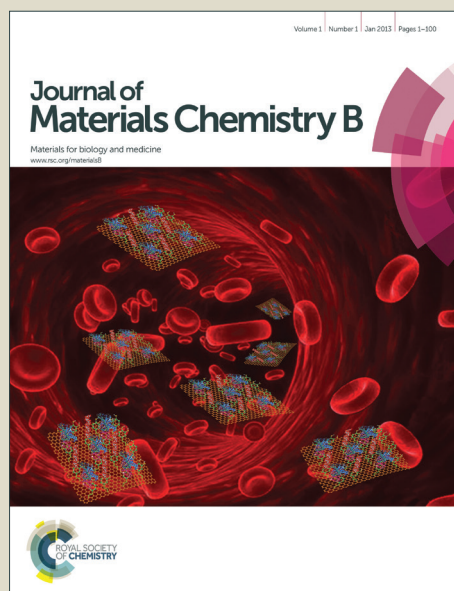


This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

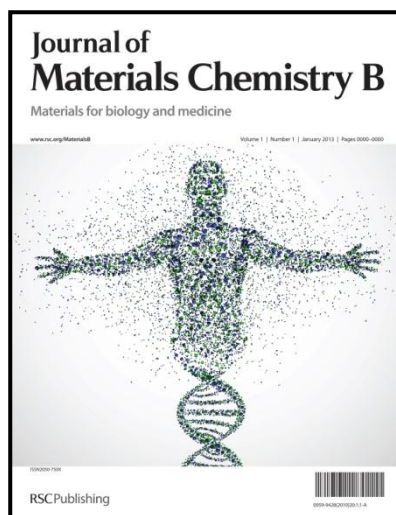

Journal of Materials Chemistry B

Materials for Biology and Medicine

Communication submission

Journal of Materials Chemistry B is a weekly journal in the materials field. The journal is interdisciplinary, publishing work of international significance on all aspects of materials chemistry related to biology and medicine. Articles cover the fabrication, properties and applications of materials.

2012 Impact Factor of *Journal of Materials Chemistry*: **6.10**

For more information go to www.rsc.org/materialsB

The following paper has been submitted to *Journal of Materials Chemistry B* for consideration as an urgent **communication**.

Journal of Materials Chemistry B wishes to publish original research that demonstrates **novelty and advance**, either in the chemistry used to produce materials or in the properties/applications of the materials produced. Work submitted that is outside of these criteria will not usually be considered for publication. The materials should also be related to the theme of materials for biology and medicine. Furthermore, communications must demonstrate sufficient **quality and urgency** to warrant publication in that form.

Routine or incremental work, however competently researched and reported, should not be recommended for publication if it does not meet our expectations with regard to novelty and impact.

It is the responsibility of authors to provide fully convincing evidence for the homogeneity and identity of all compounds they claim as new. Evidence of both purity and identity is required to establish that the properties and constants reported are those of the compound with the new structure claimed.

Thank you for your effort in reviewing this submission. It is only through the continued service of referees that we can maintain both the high quality of the publication and the rapid response times to authors. We would greatly appreciate if you could review this paper in **one week**. Please let us know if that will not be possible.

Once again, we appreciate your time in serving as a reviewer. To acknowledge this, the RSC offers a **25% discount** on its books: <http://www.rsc.org/Shop/books/discounts.asp>. Please also consider submitting your next manuscript to *Journal of Materials Chemistry B*.

Best wishes,

Liz Dunn
Managing Editor, *Journal of Materials Chemistry B*

COMMUNICATION

Photoactive Electrospun Polymeric Meshes: Spatiotemporally Wetting of Textured 3-Dimensional Structures

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

J. S. Hersey, J. D. Freedman, and M. W. Grinstaff*

DOI: 10.1039/x0xx00000x

www.rsc.org/

The preparation, characterization, and use of a UV responsive non-woven nanofiber polymeric mesh is reported that transitions from being hydrophobic to hydrophilic. Three distinct wetting profiles are observed during the wetting process. 3D hydrophilic cavities were created within the hydrophobic bulk material by using a photomask to control the geometry and UV exposure time to control the depth of the region.

Control over polymeric material properties such as phase transition temperatures,¹ degradation rates,² and/or hydrophobicity³ are of interest for many biomedical and industrial applications.⁴ Methods that enable real-time alteration or spatial control over these property changes are of particular utility as it provides even greater control and functionality.⁵ As such, approaches employing external triggers like temperature,⁶ pH,^{3b, 7} and light^{5, 8} offer significant opportunities to address this need.^{4a} Our interest is in polymeric meshes or scaffolds where changes in hydrophobicity can be induced using light to afford wetting of a material at the surface and bulk. Herein, we describe the fabrication of photoresponsive electrospun polymeric nano-fiber meshes, the transition from a hydrophobic to a hydrophilic material upon light exposure, the kinetics of the wetting process and its agreement with previous theoretical work, the creation of defined three-dimensional (3D) hydrophilic cavities within the mesh, the characterization of these cavities using X-ray microCT imaging, and use of these materials for a pilot protein adsorption/cell patterning study.

Photoactivated wetting of a surface can be either reversible or irreversible.⁹ Surfaces displaying reversible changes in hydrophobicity upon exposure to UV light rely on strategies such as inducing the cis-to-trans transition in azobenzene derivatives¹⁰ or creating photogenerated electrons or holes in titanium oxide or zinc oxide materials.¹¹ Non-reversible light induced hydrophobicity changes typically rely on photolabile protecting groups which cleave in the presence of light exposing more hydrophilic moieties.⁵ A common and extensively studied family of photolabile protecting groups is the ortho-nitrobenzyl derivatives, where upon excitation at long wavelength UV light (~365 nm), the group is cleaved.¹² Within this family, the 1-(2-nitrophenyl) ethyl (NPE) protecting group is particularly advantageous since it cleaves faster and forms a less

harmful nitroso ketone rather than a nitrosoaldehyde compared to the ortho-nitrobenzyl group.^{12b} Consequently, we selected this group for protection of a carboxylic acid, and then this photoactive functionality was linked to the secondary hydroxyl of a glycerol repeat unit in a co-polymer composed of glycerol and 6-hydroxycaproic acid for subsequent mesh formation.

Specifically, poly(glycerol-co-ε-caprolactone) (1:4) (PGC) was synthesized following a previously published protocol,¹³ and 12-(1-(2-nitrophenyl)ethoxy)-12-oxododecanoic acid (C12-NPE) was attached to the free hydroxyl of the PGC through an ester linkage using a DCC coupling method. The UV active polymer, poly(glycerol 12-(1-(2-nitrophenyl)ethoxy)-12-oxododecanoic acid-co-caprolactone) (PGC-C12-NPE; 8.2 kg/mol), was dissolved in a 5:1 chloroform:methanol solution with poly(ε-caprolactone) (PCL) (70-90 kg/mol, Sigma) at a 3:7 weight ratio. The resulting polymer solution, at 10% by weight, was electrospun to give photoresponsive meshes. Scanning electron microscopy reveals micrometer (~3-5 μm beads) and nanometer (fiber diameters ~100-150 nm) scale textures on the surface (see supporting information for experimental details).

NMR spectroscopy was used to confirm the photolysis of the NPE group from the polymeric mesh side chains after various UV exposure times. The integration of the peak at ~6.3ppm, which corresponds to the lone hydrogen on the carbon linking the NPE

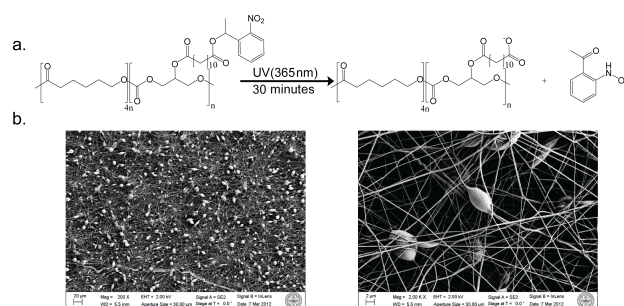


Figure 1. (a) Photoactive cleavage of NPE group yielding an exposed carboxylic acid and a nitroso ketone byproduct. (b) SEM images of electrospun PGC-C12-NPE : PCL (3:7) meshes (200x magnification (left), 2000x magnification (right))

group to the alkyl chain, was followed (Figure S1). An exponential fit was applied to the deprotection kinetics resulting in a strong correlation with the data ($R^2=0.9975$) where after 15 minutes of exposure 61.8 \pm 24% of the NPE groups were deprotected and after 60 minutes 99.1 \pm 1.5% of the groups were removed ($n=3$). No backbone polymer degradation was observed via GPC analysis, even after 120 minutes (21.6 J/cm²) of UV exposure (Table S1).

Next, a series of electrospun \sim 80 μ m thick meshes were then exposed to UV light ($\lambda = 365$ nm,) for 0, 15, 30, 60, 90, and 120 minutes. The photoactive electrospun PGC-C12-NPE mesh exhibited a UV induced transition from a hydrophobic material, with an apparent contact angle (ACA) of \sim 135°, to a hydrophilic material with an ACA of \sim 0° after various UV exposure times (Figure 2a and Figure S2). SEM analysis of before and after photolysis showed no significant difference in fiber diameter or morphology (Figure S3). A UV dose dependent wetting profile was observed with smaller UV doses wetting more slowly over time compared to larger UV doses (5.4 J/cm² vs. 10.8 J/cm² for 30 minutes and 60 minutes of UV exposure, respectively). With as little as 15 minutes of UV exposure, the ACA decreased dramatically over 600 seconds compared to the unexposed control meshes (ACA \sim 20° vs. \sim 135°) (Figure S2). Doubling the UV exposure time to 30 minutes resulted in more consistent ACAs and a fully wetted surface (ACA \sim 0°) within 300 seconds. For all UV exposure times greater than 30 minutes, the change in ACA from the native mesh was statistically significant after 120 seconds of wetting ($p < 0.05$). For reference, the contact angle of a cast film of the polymer has a contact angle of 113° before UV irradiation and a contact angle of 108° after UV irradiation (120 minutes, 21.6 J/cm²).

Upon closer inspection of the wetting profiles, three distinct transitions were observed during the wetting process (Figure 2b and S4). The initial wetting rate is dictated by the Cassie-Baxter to Wenzel transition where air is slowly displaced by the water directly below it at a rate of -0.91 ± 0.39 degrees per second. However, once the droplets reach a critical ACA of \sim 110°, the wetting rate dramatically increases by approximately 4 fold (-0.91 ± 0.39 °/second

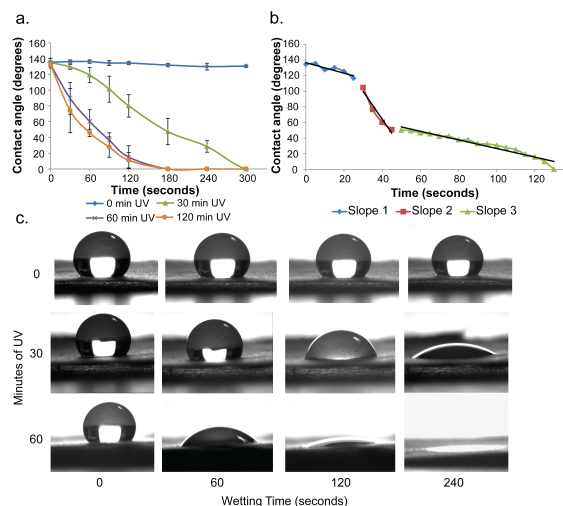


Figure 2. (a) UV induced hydrophobicity change from hydrophobic (\sim 135°) to hydrophilic (\sim 0°) ACA after 30, 60, or 120 minutes of UV exposure. The ACA of water (4 μ l) on the electrospun polymeric mesh surface was measured over 300 seconds. ($n=3$; Avg \pm SD) (b) Three distinct wetting rates for a mesh exposed to 120 minutes of UV exposure. (c) Images of a water droplet on meshes after exposure to 0, 30, or 60 minutes of UV light as a function of time.

vs. -3.43 ± 0.46 °/second) as the contact angle drops to \sim 50° (Table S2). The ACA then continues to decrease at a similar rate as to the initial wetting rate, until the droplet fully wets the surface (ACA = 0°) (Figure S4). Fortunately, previous theoretical work has examined this phenomenon of wetting on a hydrophilic rough surface. Ishino et al. describes this phenomenon of hydrophilic rough surfaces as a transition from the Cassie to Wenzel to Sunny-side-up state where

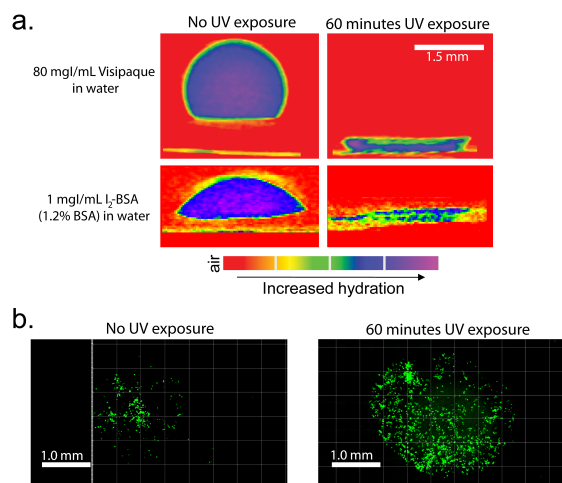


Figure 3. (a) μ CT imaging of 7:3 PCL:PGC-C12-NPE electrospun meshes exposed to either 0 minutes (left) or 60 minutes (right) of 365 nm UV light through a 1590 μ m in diameter photomask. Visipaque (left) in water or an I₂-BSA solution (right) was used to track wetting/adsorption into the mesh. (b) Fluorescence images of MCF7 cells (green) seeded onto meshes exposed to 0 minutes (left) and 60 minutes (right) of UV light.

the water begins to penetrate a rough surface beyond the boundaries of the water droplet on the surface such that it appears like a sunny-side-up egg.¹⁴

We next evaluated the utility of this photoinduced wetting method to print 3D hydrophilic cavities surrounded by hydrophobic regions. Specifically, cavities of 194.2 ± 8.2 μ m and 301.1 ± 55.7 μ m depths were fabricated by exposing the photoactive meshes to UV light for 30 minutes and 60 minutes, respectively, using a circular photo mask (1590 μ m in diameter). These hydrophilic regions were analysed by applying a dilute solution of a water soluble CT contrast agent (Visipaque, 80 mg of iodine per mL water, Figure S5) to the surface of the meshes and using an X-ray μ CT scanner to measure the water penetration into the meshes. As shown in Figure 3a, the aqueous CT contrast agent solution was restricted to the surface of the hydrophobic mesh, and only after UV photolysis did it penetrate into the cavities. A linear relationship between the UV exposure time and the depth of the cavities was observed (Figure S6). However, the diameter of the cavities was not as well defined. The photomask was 1590 μ m in diameter while the average cavity diameters were 5803.9 ± 138.1 μ m and 2709.1 ± 485.2 μ m for the 30 minute and 60 minute exposure times respectively ($n=3$). This indicates that the hydrophobicity of the material is anisotropic where layers through the thickness of the material (XY plane: perpendicular to the fibers) are hydrophobic but across the plane of any given layer (XZ and YZ planes: parallel to the fibers), the material's hydrophobicity is likely reduced. For the 60 minute UV exposure time point, the water infiltrates farther into the mesh and thus does not spread as much leading to a smaller diameter cavity.

These imaging results also provide insight into the mechanism of wetting as discussed earlier. The initial wetting is a result of a Cassie to Wenzel transition; however, the other two wetting rates may be associated with the anisotropic hydrophobicity of the materials where the water penetrates through XY planes more quickly than it does through XZ or YZ planes. The rapid wetting is likely a combination of the water flowing into the mesh (i.e., through photolyzed XY planes) and along the fibers of each XY plane (i.e., along the XZ and YZ planes). Once the water has reached the final deprotected XY plane, the remaining wetting is only associated with the spreading along the XY planes through the XZ and YZ planes which justifies the slower rate.

One potential application for a material with tunable hydrophobicity throughout its 3D structure is selective protein/cell patterning. A number of different strategies are used to adhere cells to a surface including the grafting of small peptides that bind to specific cell receptors (e.g., RGD); however, we will use the well-known phenomenon of protein adsorption to a surface followed by cell attachment for this pilot experiment.¹⁵ In order to observe protein adsorption to the wetted regions of mesh via CT, an iodinated bovine serum albumin (I₂-BSA) was prepared¹⁶ as a model system. As before, a photolyzed cavity was prepared and a 1.2% I₂-BSA solution (1 mgI/mL) was used to observe protein adsorption to the hydrophilic cavity as shown in Figure 3a where the protein adsorbs within the same 3D region as water. Next, we determined whether a human breast cancer cell line (MCF7) in fetal bovine serum containing media would selectively adhere on the hydrophilic regions of the UV active meshes. Using a live cell fluorescent stain and confocal microscopy, we observed cells adhered in the regions where the mesh wets and protein adsorbs (~2.7 mm in diameter cavities). In addition, there are approximately twice as many cells alive after 24 hours on the mesh exposed to UV light compared to the untreated control. We could not observe cells below the first layer due to poor light transmittance through the mesh, but given the porosity of the mesh (1-2 microns) we expect the majority of the cells to be at the top layer.¹⁷ Present efforts are focused on preparing a UV active mesh and procedure that allows for finer control over both the shape and the depth of hydrophilic regions printed as well as exploring different electrospinning parameters to vary mesh porosity, fiber diameter and thickness. These patterned materials maybe of interest for those conducting high throughput drug screening assays, studying cell-scaffold interactions, or studying the interactions between various cell types when arranged in predefined architectures.¹⁸

Conclusions

A photoactive non-woven nano-fiber hydrophobic mesh is reported that responds to UV light by becoming permanently more hydrophilic. A linear relationship between UV exposure and contact angle is observed with the rate of wetting increasing with greater UV exposure. SEM analysis reveals a mesh composed of nano-fibers and micro-beads with diameters between ~100-150 nm and ~3-5 μ m, respectively, and is unchanged after photolysis. This morphology contributes to the roughness of the material, by enhancing the hydrophobicity and hydrophilicity of the material. A dynamic wetting profile is observed with three distinct wetting rates. Hydrophilic 3D cavities can be created within the hydrophobic mesh using a photomask and UV exposure time to control the shape and depth of the hydrophilic regions, respectively. Mesh or scaffold materials possessing differing degrees of hydrophobicity at the surface and the bulk are of significant interest for a variety of industrial, biotechnology, and biomedical applications. This facile approach enables selective wetting of 3D regions within a material


opening up additional avenues of investigation where real-time control of polymer properties are key.

This work was supported in part by the BU Nanomedicine Program and Cross-Disciplinary Training in Nanotechnology for Cancer (NIH R25 CA153955), the BU Nanotheranostics ARC, and the BU T32 Grant entitled Translational Research in Biomaterials (NIH T32EB006359).

Notes and references

- ^a Departments of Biomedical Engineering and Chemistry, Boston University, Boston, MA 02215. † Electronic Supplementary Information (ESI) available: Detailed experimental methods, synthesis, characterization, and supporting figures See DOI: 10.1039/c000000x/
- 1 a) A. Lendlein and T. Sauter, *Macromol. Chem. Phys.*, **2013**, *214*, 1175-1177; b) M. C. Serrano and G. A. Ameer, *Macromol. Biosci.*, **2012**, *12*, 1156-1171
- 2 a) K. E. Uhrich, S. M. Cannizzaro, R. S. Langer and K. M. Shakesheff, *Chem. Rev.*, **1999**, *99*, 3181-3198; b) H. Zhang and M. W. Grinstaff, *J. Am. Chem. Soc.*, **2013**, *135*, 6806-6809.
- 3 a) J. P. Jain, M. Sokolsky, N. Kumar and A. J. Domb, *Polym. Rev.*, **2008**, *48*, 156-191; b) A. P. Griset, J. Walpole, R. Liu, A. Gaffey, Y. L. Colson and M. W. Grinstaff, *J. Am. Chem. Soc.*, **2009**, *131*, 2469-2471; c) S. Einmahl, S. Capancioni, K. Schwach-Abdellaoui, M. Moeller, F. Behar-Cohen and R. Gurny, *Adv. Drug Delivery Rev.*, **2001**, *53*, 45-73
- 4 a) M. A. C. Stuart, W. T. Huck, J. Genzer, M. Müller, C. Ober, M. Stamm, G. B. Sukhorukov, I. Szleifer, V. V. Tsukruk and M. Urban, *Nat. Mater.*, **2010**, *9*, 101-113; b) S. Ahn, R. M. Kasi, S.-C. Kim, N. Sharma and Y. Zhou, *Soft Matter*, **2008**, *4*, 1151-1157.
- 5 I. Tomatsu, K. Peng and A. Kros, *Adv. Drug Delivery Rev.*, **2011**, *63*, 1257-1266.
- 6 a) H. Hayashi, K. Kono and T. Takagishi, *Biochim. Biophys. Acta, Biomembr.*, **1996**, *1280*, 127-134; b) R. Liu, M. Fraylich and B. R. Saunders, *Colloid Polym. Sci.*, **2009**, *287*, 627-643; c) A. Chilkoti, M. R. Dreher and D. E. Meyer, *Adv. Drug Delivery Rev.*, **2002**, *54*, 1093-1111.
- 7 a) C. Donini, D. Robinson, P. Colombo, F. Giordano and N. Peppas, *Int. J. Pharm.*, **2002**, *245*, 83-91; b) M. E. Harmon, D. Kuckling and C. W. Frank, *Macromolecules*, **2003**, *36*, 162-172.
- 8 a) S. R. Lustig, G. J. Everlof and G. D. Jaycox, *Macromolecules*, **2001**, *34*, 2364-2372; b) M. W. Tibbitt, A. M. Kloxin, K. U. Dyamenahalli and K. S. Anseth, *Soft Matter*, **2010**, *6*, 5100-5108; c) C. A. DeForest and K. S. Anseth, *Angew. Chem. Int. Ed. Engl.*, **2012**, *51*, 1816-1819; d) J. S. Katz and J. A. Burdick, *Macromol. Biosci.*, **2010**, *10*, 339-348.
- 9 S. Wang, Y. Song and L. Jiang, *J. Photochem. Photobiol., C*, **2007**, *8*, 18-29.
- 10 a) I. Willner, S. Rubin and T. Zor, *J. Am. Chem. Soc.*, **1991**, *113*, 4013-4014; b) H. S. Lim, J. T. Han, D. Kwak, M. Jin and K. Cho, *J. Am. Chem. Soc.*, **2006**, *128*, 14458-14459.
- 11 a) A. Nakajima, K. Hashimoto, T. Watanabe, K. Takai, G. Yamauchi and A. Fujishima, *Langmuir*, **2000**, *16*, 7044-7047; b) Y. Li, W. Cai, G. Duan, B. Cao, F. Sun and F. Lu, *J. Colloid Interface Sci.*, **2005**, *287*, 634-639.
- 12 a) C. G. Bochet, *J. Am. Chem. Soc.*, **2002**, *125*, 125-142; b) G. Mayer and A. Heckel, *Angew. Chem., Int. Ed.*, **2006**, *45*, 4900-4921.
- 13 J. B. Wolinsky, W. C. Ray, Y. L. Colson and M. W. Grinstaff, *Macromolecules*, **2007**, *40*, 7065-7068.
- 14 C. Ishino and K. Okumura, *Eur. Phys. J. E*, **2008**, *25*, 415-424.
- 15 E. Ostuni, C. S. Chen, D. E. Ingber and G. M. Whitesides, *Langmuir*, **2001**, *17*, 2828-2834.
- 16 R. L. Perlman and H. Edelhoch, *J. Biol. Chem.*, **1967**, *242*, 2416-2422.
- 17 N. E. Zander, J. A. Orlicki, A. M. Rawlett and T. P. Beebe Jr, *J. Mater. Sci.: Mater. Med.*, **2013**, *24*, 179-187.
- 18 a) T. G. Fernandes, M. M. Diogo, D. S. Clark, J. S. Dordick and J. Cabral, *Trends Biotechnol.*, **2009**, *27*, 342-349; b) D. H. Kim, H. Lee, Y. K. Lee, J. M. Nam and A. Levchenko, *Adv. Mater.*, **2010**, *22*, 4551-4566; c) N. N. Kachouie, Y. Du, H. Bae, M. Khabiry, A. F. Ahari, B. Zamanian, J. Fukuda and A. Khademhosseini, *Organogenesis*, **2010**, *6*, 234-244; d) P. Kingshott, G. Andersson, S. L. McArthur and H. J. Griesser, *Curr. Opin. Chem. Biol.*, **2011**, *15*, 667-676.

TOC

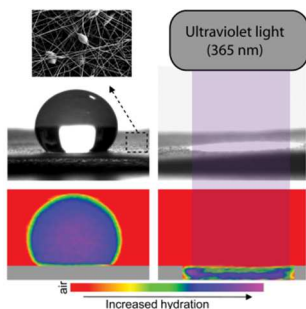

A non-woven nanofiber/microbead polymeric mesh is reported that transitions from being hydrophobic to hydrophilic upon photolysis.