

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Probing the Interaction of Rh, Co and Bimetallic Rh-Co Nanoparticles with CeO₂ Support: Catalytic Materials for Alternative Energy Generation

E. Varga,^a P. Pusztai,^b L. Óvári,^c A. Oszkó,^a A. Erdőhelyi,^a C. Papp,^d H.-P. Steinrück,^d
Z. Kónya,^{b,c} J. Kiss,^{a,c*}

^aDepartment of Physical Chemistry and Materials Science, University of Szeged, H-6720 Szeged, Aradi v.t. 1

^bDepartment of Applied and Environmental Chemistry, University of Szeged, H-6720 Szeged,

^cMTA-SZTE Reaction Kinetics and Surface Chemistry Research Group, H-6720 Szeged, Rerrich B. t. 1., Hungary

^dChair of Physical Chemistry II, University of Erlangen-Nürnberg, Egerlandstr.3, 91058 Erlangen, Germany

ABSTRACT:

The interaction of CeO₂-supported Rh, Co and bimetallic Rh-Co nanoparticles, which are active catalysts in hydrogen production via steam reforming of ethanol, a process related to renewable energy generation, were studied by X-ray diffraction (XRD), high resolution electron microscopy (HRTEM), X-ray photoelectron spectroscopy (XPS) and low energy ion scattering (LEIS). Furthermore, diffuse reflectance infrared spectroscopy (DRIFTS) of adsorbed CO as a probe molecule was used to characterize the morphology of metal particles. At small loadings (0.1%), Rh is in a much dispersed state on ceria, while at higher contents (1-5%), Rh forms 2-8 nm particles. Between 473-673 K pronounced oxygen transfer from ceria to Rh is observed and at 773 K significant agglomeration of Rh occurs. On reduced ceria, XPS indicates a possible electron transfer from Rh to ceria. The formation of smaller ceria crystallites upon loading with Co was concluded from XRD and HRTEM; for 10% Co, the CeO₂ particle size decreased from 27.6 to 10.7 nm. Strong dissolution of Co into ceria and a certain extent of encapsulation by ceria were deduced by XRD, XPS and LEIS. In the bimetallic system, the presence of Rh enhances the reduction of cobalt and ceria. During thermal treatments, reoxidation of Co occurs, and Rh agglomeration as well as oxygen migration from ceria to Rh are hindered in the presence of cobalt.

Keywords: cobalt, rhodium, ceria, Rh-Co bimetallic materials, XPS, LEIS, XRD, HRTEM

1. INTRODUCTION

Hydrogen is expected to play a key role in future energy technology as an efficient energy carrier.¹⁻³ Great efforts are currently made to produce hydrogen by heterogeneous catalytic processes from renewable sources. This demand inspired studies on the dehydrogenation of oxygenated hydrocarbons including alcohols. These materials, which are obtained by the fermentation of agricultural wastes, can be important carbon-neutral renewable energy sources, and also renewable raw materials for the chemical industry.⁴⁻⁷

Ceria-supported precious metal catalysts such as Rh, Pd, and Pt are widely used in many important applications, including three-way automobile emission-control catalysis, fuel cells, and also hydrogen production from ethanol. This is due to the peculiar redox properties and oxygen storage capacity of ceria, as well as to synergetic effects between the ceria support and metals.⁸⁻¹³ Noble metals, especially Rh, have proven to be excellent catalysts for dehydrogenation reactions,¹⁴⁻¹⁶ but their prices are prohibitively high. As an alternative, the less expensive transition metal Co is a promising catalyst for the steam reforming of ethanol (SRE). As a consequence of the Co-promoted C-C bond rupture in adsorbed ethanol, Co on CeO₂ and on other supports achieves high ethanol conversion and selectivities of H₂ and CO₂, even at relatively low temperatures (~723 K).¹⁷⁻¹⁹ While recent studies suggested that Co²⁺ sites are the active centers in SRE, and that Co⁰ sites are responsible for coke formation,^{20, 21} other authors argue that metallic cobalt plays the key role in SRE.²¹ The oxygen exchange capacity of cerium oxide is associated with its ability to reversibly change the oxidation states between Ce⁴⁺ and Ce³⁺. These observations led to the outstanding attention to the catalytic properties of the Co/ceria system in ethanol transformation reactions, including SRE.^{12, 17-28}

Very recently we have found that trace amounts of Rh promoter (0.1wt% - 0.17 mol%) dramatically altered the reaction pathways of SRE on Co/ceria catalysts. In contrast to Co/ceria, on rhodium-containing Co/ceria catalysts no acetone was observed. The addition of a small amount of Rh as a promoter, however, resulted in a significant increase in the hydrogen selectivity.^{29, 30} Bimetallic Rh-Co catalysts supported on MgO showed also high activity in the partial oxidation of methane.^{31, 32} Similar catalytic systems (Pt-Ni, Pd-Ni, Rh-Ni) give high methane conversion in the oxidative steam reforming of CH₄.³³⁻³⁵ Rh containing bimetallic catalysts show high efficiencies in dry³⁶ and steam³⁵ reforming of methane.

Recently, it was demonstrated that the catalytic performance of CeO₂ depends on the particle size, due to the difference of the reducibility and therefore the number of acidic sites.³⁷ Depending on the degree of ceria reduction, also unique reactivity profiles can be observed on ceria-supported Rh catalysts. For example, while CO adsorbs non-dissociatively

on Rh nanoparticles on fully oxidized ceria films, it dissociates on partially reduced films.³⁴ Similarly, NO dissociation is enhanced when Rh particles are supported on reduced CeO₂(111).^{38,5} Several hypotheses have been put forward, including electron transfer from ceria to Rh particles, structural variation in the Rh particles, or O spillover from Rh to ceria.^{35,36} Low-temperature oxygen migration from ceria to Rh is also proposed in the ceria-rhodium interaction.^{37,38}

The growth of Co on CeO₂(111) was briefly studied previously using XPS. Based on the linear dependence of the Ce 3d/Co 2p intensity ratio vs. cobalt coverage, two dimensional growth of Co was proposed up to 1 ML.²¹ Recent low energy ion scattering spectroscopy (LEIS) and XPS studies showed, however, that the growth mode is rather three dimensional.³⁹ From the Co 2p peak shape, the resulting surface species were identified as Co⁰ and Co²⁺. Furthermore, reduction of Ce was observed upon Co deposition, due to the reaction of Co with CeO₂.^{21, 28, 39} A significant part of cobalt (Co²⁺) dissolved into the CeO₂(111) film, as was detected by LEIS.³⁹ On mesoporous ceria, metallic cobalt cannot be prepared using cobalt salts as a precursor. Even after strong reduction with hydrogen, the majority of cobalt remained in the oxidized Co²⁺ state.^{24, 25, 29, 30} When a small amount (0.1%) of Rh was added to the Co/ceria system, the reducibility was enhanced dramatically. This was concluded from the reaction temperature of cobalt during temperature reduction experiments (TPR) and from the lower binding energy of the Co 2p signal in XPS. In addition, the ceria support was also reduced significantly. These effects can be explained by hydrogen spill over phenomenon.^{29, 30} Similar noble metal-induced effects were observed for alumina-supported cobalt Fischer-Tropsch catalysts,^{40, 41} and on other bimetallic cobalt-based systems.^{36, 42-44}

It is frequently observed that the presence of a second metal can greatly influence the intrinsic surface properties of a specific metal. It is emphasized that in contrast to bulk alloys, nanosized bimetallic systems are extremely sensitive to the structure, morphology, and valence state of the oxide support, on which the nanoparticles were prepared.^{45, 46} "Ensemble" or "ligand" effects are frequently invoked to explain the promoting effect of the second metal.⁴⁴ Enhanced dispersion⁴⁷ and increased sintering of Au nanoparticles on TiO₂(110) were observed in the presence of a second metal.⁴⁸ It was also observed that the second metal (Rh, Pt, Pd) significantly changed the morphology, topology and reactivity of the other metal (Au, Mo) on oxides.⁴⁹⁻⁵³ STM and LEIS experiments revealed that the metal may completely and uniformly cover the second metal nanoparticles.^{54, 55}

An important aim of this study is to understand the enhanced catalytic effects of the ceria-supported Rh-Co bimetallic catalyst in SRE. For this purpose, we map the variety of possible

interactions between rhodium and cobalt on ceria support. As ceria itself is an active support in mono- and bimetallic catalysts, the metal-support interaction is also examined. X-ray diffraction (XRD) and high resolution transmission electron microscopy (HRTEM) give valuable data about the structure and morphology of nanoparticles. X-ray photoelectron spectroscopy (XPS) is an excellent tool to describe the oxidation states of the elements and to follow the charge transfer from metal to metal, and from the metal to the support and back in mono and bimetallic catalysts.^{56, 57} While XPS provides important data from the top surface layers of a sample (down to a depth of a few nanometers), LEIS supplies information almost exclusively about the outermost atomic layer.^{58,59} These two methods, complemented with energy-dispersive X-ray spectroscopy (EDX), provide a comprehensive characterization of the surface and bulk composition of complex catalytic systems.

Herein, we first investigate Rh/ceria catalysts, then we focus on the Co/ceria systems and finally turn to ceria supported Rh-Co bimetallic catalysts. As a dramatic influence on the catalytic properties in the steam reforming of ethanol was observed even for very small amounts of Rh promoter, the investigations concentrate mainly on (0.1wt% Rh + 2wt% Co)/CeO₂ and on (0.1wt% Rh + 10wt% Co)/CeO₂ catalysts. Moreover, in order to get closer to the catalytic conditions, we applied the same pretreatment that was used in the catalytic reactions.

2. EXPERIMENTAL

The catalysts were prepared by impregnating the CeO₂ support (Alfa Aesar, 43 m²/g) with the aqueous solution of Co(NO₃)₂ to yield nominal metal contents of 2 wt% (5.6 mol%) or 10 wt% (28.0 mol%). The impregnated powders were dried at 383 K, calcined at 973 K and pressed to pellets. Rh containing samples (0.1 wt% = 0.17 mol%, 1 wt% = 1.7 mol%, 5 wt% = 8.5 mol%) were prepared by the same impregnation method from RhCl₃ x 3H₂O (Johnson Matthey). Prior to impregnation, the ceria support was calcined at 973 K. The Rh-Co bimetallic samples were prepared by sequential impregnation and calcination with Co, and thereafter with Rh.²⁹ Before the measurements, fragments of catalyst pellets were oxidized at 673 K in flowing O₂ for 20 min and reduced at 773 K in flowing H₂ for 60 min. The hydrogen was replaced by nitrogen within few seconds, and the sample was cooled down in inert atmosphere. In our XPS measurements it was observed that on the ceria-supported samples only minor amounts of adventitious carbon adsorb, and that at high Rh content a distinct Cl 2p peak is also present on the survey spectra originated from the RhCl₃ reagent. After pretreatment all these contaminants were found to be removed (Fig. S1).

The BET surface and pore volume measurements of the catalysts were carried out by a Quantachrome NOVA 3000e instrument using N₂ adsorption at liquid nitrogen temperature (Table 1). The surface areas and pore sizes are consistent with a mesoporous material.^{25, 29}

For XPS studies, the powder samples were pressed into pellets with ca. 1 cm diameter and a few tenth of mm thickness. Sample treatments were carried out in a high-pressure cell (catalytic chamber) connected to the analysis chamber via a gate valve. The samples were pre-treated in the same way as described above. After the pre-treatment, they were cooled down to room temperature in flowing nitrogen. Then, the high-pressure cell was evacuated; the sample was transferred to the analysis chamber in high vacuum (i.e., without contact to air), where the XP spectra were recorded. As the next step, the sample was moved back into the catalytic chamber, where it was heated under flowing N₂ up to 773 K in 100 K steps. XP spectra were taken with a SPECS instrument equipped with a PHOIBOS 150 MCD 9 hemispherical electron energy analyzer, using Al K_α radiation ($h\nu = 1486.6$ eV). The X-ray gun was operated at 210 W (14 kV, 15 mA). The analyzer was operated in the FAT mode, with the pass energy set to 20 eV. The detection angle of electrons was 20° with respect to surface normal. Typically five scans were summed to get a single spectrum. For data acquisition and evaluation both manufacturer's (SpecsLab2) and commercial (CasaXPS, Origin) software were used. The binding energy scale was corrected by fixing the Ce 3d u''' peak (see below) to 916.6 eV. The deconvolution of the high-resolution spectra was performed using the Curved background type and the symmetric components were fitted with a common Gaussian–Lorentzian (70:30) line shape. For Rh 3d and Co 2p signals, the peak shapes of metallic Rh and Co, CoO and Co₃O₄ reference samples were applied.

A SPECS IQE 12/38 ion source was used for LEIS spectra. He⁺ or Ne⁺ ions of 800 eV kinetic energy were applied at a low ion flux (0.2 μA/cm²), which was necessary to minimize the sputtering of the surface. During acquisition the samples were flooded with electrons possessing 1-2 eV energy to compensate the electrostatic charging. The incident angle was 55° (with respect to surface normal), ions ejected along the surface normal were detected. The ion energies were measured by the same hemispherical energy analyzer as mentioned above. Etching processes were performed with the same ion source with the use of 4 keV Ar⁺ ions up to 0.7 μA/cm² ion flux.

DRIFT spectra were recorded with an Agilent CARY-670 FTS-135 FT-IR spectrometer equipped with a diffuse reflectance attachment (Harrick) with BaF₂ windows. Typically 256 scans were registered at a spectral resolution of 2 cm⁻¹. All spectra were recorded at 293 K.

The whole optical path was purged with CO₂- and H₂O-free air generated by a Whatman purge gas generator.

The bulk concentration of the elements was determined by energy-dispersive X-ray spectroscopy (EDX) using a RöntecQuantax QX² spectrometer built into a Hitachi S-4700 type II cold field emission scanning electron microscope. Spectra were taken at 20 kV acceleration voltage and quantitatively analyzed by the factory standard software after automatic background subtraction and peak fitting.

The morphology of ceria and metal-modified ceria was characterized by transmission electron microscopy (FEI Tecnai G² 20 X-Twin; 200 kV operation voltage, x180000 magnification, 125 pm/pixel resolution). X-ray diffractometry (RigakuMiniFlexII; CuK_α) and electron diffraction were used to determine the crystallinity and the structure. The metal particle size distribution was determined by image analysis of the HRTEM pictures using the ImageJ software. At least five representative images of equal magnification, taken at different spots of the TEM grid were first subjected to rolling ball background subtraction and contrast enhancement, and then the diameter of the metal nanoparticles in the image was manually measured against the calibrated TEM scale bar. Each diameter distribution histogram was constructed from 200 individual nanoparticle diameter measurements.

3. RESULTS AND DISCUSSION

3.1 Reducibility of ceria, Rh/ceria, Co/ceria, bimetallic/ceria catalysts and catalytic test in the SRE

The reducibility of ceria and metal-modified ceria is very sensitive to the pretreatment of the catalysts, the reduction procedure (calcination temperature, heating rate and the mode and temperature profile of the temperature programmed reduction, TPR).^{8, 60} For details, we refer to our previous work, where we summarized our TPR data obtained under the same experimental conditions:²⁹ The pure CeO₂ support (calcined at 973 K) displays an asymmetric low temperature feature with a rate maximum at 789 K (note that its intensity gradually decreased as TPR runs were repeated, indicating a reduction in the surface region). In addition, a pronounced high temperature peak was detected at 1090 K, attributed to the bulk reduction of the ceria support.⁶¹ In agreement with literature data the reduction of Rh occurs up to 500 K.⁶¹ In the present study, the peak maxima were observed at 403, 395 and 390 K for 0.1%, 1% and 5% Rh/ceria, respectively (not shown).

Upon adding 2% Co to CeO₂, the high temperature feature at 1090 K due to bulk

reduction of ceria shows a slight increase, and an additional well-resolved doublet appeared, with peak maxima at 590 and 639 K. This characteristic reduction profile has been previously reported for Co/CeO₂,²⁵ and is consistent with a stepwise reduction scheme, first from Co₃O₄ to CoO and thereafter from CoO to metallic Co. XPS results on 2% Co/CeO₂ (see below) indicated that the reduction of Co is not complete up to 773 K. When the Co loading was increased to 10%, the intensity of the low-temperature doublet increased and shifted to lower temperatures (563 and 626 K), and the peak at around 756 K significantly intensified.²⁹ Adding Rh (0.1-5%) to 2% Co supported on CeO₂ remarkably altered the TPR profile. The doublet moved to lower temperatures (479 and 574 K in the 0.1% Rh case), with the shift being more pronounced for the lower temperature peak, i.e., for the reduction of Co₃O₄ to CoO.²⁹

In this present work, the highest reduction temperature applied in the SRE experiment is 773 K. This temperature is sufficient only for the surface reduction of ceria (and not the bulk); at the same time, the reduction of Rh is complete and only partial reduction of Co occurs.

The pretreated catalysts were tested in ethanol stream reforming (SRE). Figure 1 displays the conversion of ethanol and the hydrogen selectivity values obtained on 0.1% Rh/CeO₂, 2% Co/CeO₂, 10% Co/CeO₂ and 0.1% Rh + 2% Co/CeO₂, after 120 min reaction time at 723 K. For comparison we demonstrated the values measured on CeO₂ support, too. The highest values were obtained on the 0.1% Rh + 2% Co/CeO₂ catalyst. The Figure clearly shows that the effect of 0.1% Rh is more significant than the increase in Co loading in terms of both conversion and selectivity. Notably the Rh promoted Co catalyst exhibited constant activity after 70 min reaction time.²⁹

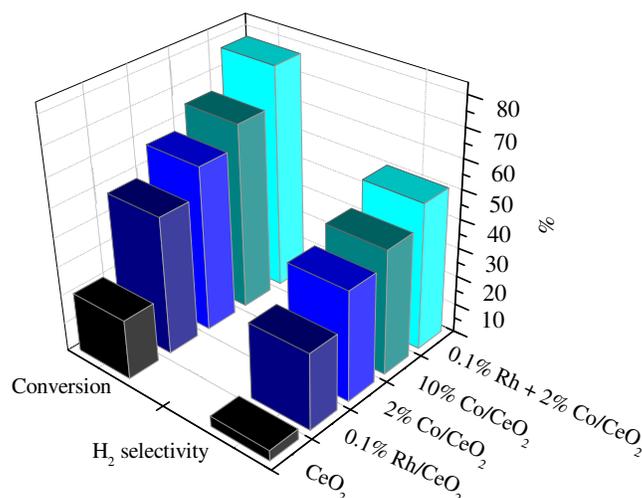


Fig. 1 Ethanol conversion and hydrogen selectivity in the EtOH + H₂O (1:3) reaction at 723 K on Co- and Rh-containing ceria based catalysts. Data are plotted at 120 min reaction time.

3.2 Characterization by powder X-ray diffraction (XRD) and transmission electron microscopy (HRTEM)

The XRD pattern of ceria, Rh/ceria and Co/ceria catalysts after calcination and oxidation/reduction process are shown in Fig. 2. In order to avoid or at least minimize re-oxidation, a glove box was used to transfer the samples from the preparation chamber to the XRD apparatus. The observed reflections (28.5° for (111), 33.0° for (200), 47.5° for (220), 56.3° for (311) and 59.1° for (222) facets of nearly stoichiometric ceria) agree well with the literature data of cubic CeO₂.^{24, 25, 62, 63} After pre-reduction at 773 K, the coordination number of Ce⁴⁺ to O²⁻ is reduced from eight to seven and Ce³⁺ ions are introduced into the crystal lattice. The Ce³⁺ ions have higher ionic radii than Ce⁴⁺ ions, and instead of the (111) lattice plane in pristine ceria, planes with higher Miller indexes became dominant because the formation of Ce³⁺ ions increased the lattice spacing.^{11, 64} This slight reduction can be detected by XPS, too (see below). Taking into account the peak broadening by the apparatus, the average size of the ceria crystallites was 27.6 nm, determined by Scherrer's method for the (111) reflection (Table 1).

When the ceria was loaded with Rh, nearly no change could be observed in the ceria diffraction pattern; only a new weak reflection appeared at 41.0° , which is identified as the Rh(111) plane (Fig. 2B). At 0.1% and 1% Rh, reflection from Rh could not be detected due to the small metal content and large dispersion. After zooming on into the diffractogram, the reflection at 41.0° for the Rh(111) plane is clearly visible for a Rh content of 5%. In addition, very small extra reflections are seen at 39.5° and 42.5° . The former originates from the sample holder, the latter is due to a ceria structure, which was identified to be different from the cubic structure. The XRD line shapes of ceria remained unchanged in the presence of Rh (Fig. 2A). For 5% Rh/ceria, where the XRD peak had sufficient intensity, we estimated the average crystallite size to 6.0 nm, which is very close to the value determined by TEM (see below). It is known from the literature that the particle size determination from TEM images is not an easy task. Idriss et al.⁶⁵ reported that TEM did not show conclusive evidence for the presence of metals on a CeO₂ support. From other work, it can be inferred that the surface area of ceria influenced the size of Rh particles. At 1% Rh content on a low surface area material (14 m²/g), where coarse CeO₂ grains are observed, the size of Rh clusters falls in the 5-20 nm range; on a high surface area CeO₂ support (275 m²/g), the size varied from 4 to 8 nm.⁶⁶

In our case, the surface areas of the supported catalysts were 19.8-17 m²/g (Table 1), depending on the Rh content (0.1%-5%). The Rh particle size varied between 2.4-6.5 nm on 1% Rh/ceria and on 5% Rh/ceria. In the latter case, a small portion of the particles was around 10 nm in size. The typical HRTEM images are shown in Fig. 3. For 0.1% Rh/ceria, the particle size determination was ambiguous due to the very low content and high dispersion. It is important to note that the Rh loading did not alter the ceria particle sizes (Table 1).

Table 1. Some Physical Parameters of Bare Supports and Co and Rh Loaded Catalyst*

Catalyst*	$S_A(m^2/g)$	Total pore volume(cm^3/g) at $p/p_0=0.99$	Average pore radius (nm)	CeO ₂ particle size** (nm)	Co/Rh atomic ratio
CeO ₂	21.5	0.156	14.5	27.6	-
2% Co/CeO ₂	7.4	0.045	12.3	17.1	-
10% Co/CeO ₂	6.8	0.041	11.7	10.7	-
0.1% Rh/CeO ₂	19.8	0.148	14.2	27.6	-
0.1% Rh+ 2% Co/CeO ₂	7.6	0.050	13.3	17.0	34.9
1% Rh/CeO ₂	18.6	0.120	13	26.7	-
5% Rh/CeO ₂	17.0	0.109	12.5	26.5	-
0.1% Rh + 10% Co/CeO ₂	6.9	0.048	13.1	11.1	174.5
1% Rh + 2% Co/CeO ₂	7.8	0.050	12.8	24.1	3.5

*The samples were calcined at 973 K. ** Determined from XRD after reduction.

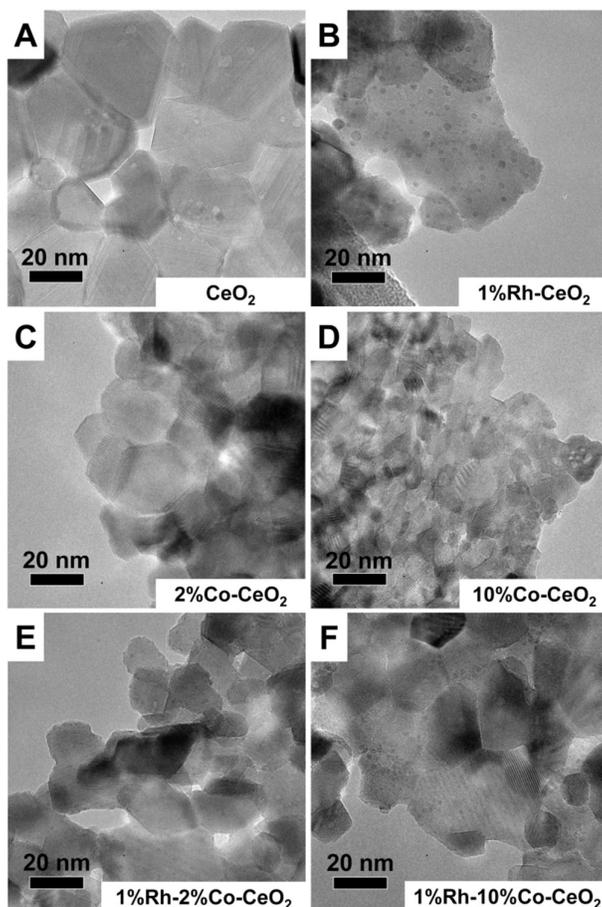


Fig. 3 TEM images of ceria and ceria supported Rh, Co and Rh-Co catalysts

The XRD patterns of Co-containing ceria (2% and 10%) are also presented in Fig. 2. On oxidized Co-containing samples, apart from the ceria reflections very weak extra reflections appeared, which are attributed to Co_3O_4 (31.5° for (220), 36.9° for (311) and 65.2° for (400)). The average crystallite size of Co_3O_4 was calculated to be 22.5 nm from the (311) reflection. In contrast to the oxidized catalysts, Co_3O_4 , CoO and Co phases are very difficult to observe on the reduced catalysts. In the literature, only a very weak reflection was reported at 44° for metallic Co at a similar reduction temperature, even for 10% Co content in ceria.²⁵ The lack of Co^{2+} or Co reflections can be explained by a significant dissolution of Co into ceria. Our previous XPS and LEIS work on a $\text{Co}/\text{CeO}_2(111)$ model catalyst demonstrated that above 750 K Co significantly penetrated into the ceria support.³⁹ Notably, the ceria peak positions do not change due to Co-loading; however, at the same time, the peaks significantly broadened, particularly at 10% Co content (Fig. 2A). This behavior, in agreement with the HRTEM images (Fig. 3C and D), indicates that the presence of Co induces a disruption process in the

ceria phase. Calculations using Scherrer's method for the (111) reflection of CeO_2 show that the ceria crystallite size became smaller, 17.1 nm for 2% Co/ceria, and 10.7 nm for the 10% Co/ceria catalyst (Table 1). While the high temperature hydrogen treatments (reduction) play an important role in the disruption phenomenon, the oxidation step did not cause such a dramatic effect: for the 10% Co/ceria catalyst, the ceria particle size decreased from 27.6 to 16.9 nm upon oxidation of the calcined Co-containing sample at 673 K. In agreement with a literature observation,⁶³ Co-oxides and metallic Co particles are difficult to distinguish in HRTEM from the CeO_2 particles, due to the low contrast and the above mentioned significant dissolution.

For the Rh-Co bimetallic cases, a similar broadening of the ceria reflections takes place, though to a lesser extent than for Co/ceria samples (Fig. 2A). In the case of 1% Rh + 10% Co/ceria, the ceria particle size was calculated to be 17.1 nm; the respective value without Rh was 10.7 nm. This behavior indicates that this small amount of Rh may inhibit the Co-induced disruption of ceria. A similar moderate change was observed for 1% Rh + 2% Co/ceria (Table 1). It is important to note that new reflections were not observed for the bimetallic system.

3.3 CO adsorption on Rh/ceria and Co-Rh/ceria, DRIFTS experiments

The morphology of Rh supported on CeO_2 was also investigated by FTIR, employing adsorbed CO as a probe molecule, which is sensitive to the local surface structure (Fig. 4). Adsorbed CO exhibits at least three different $\nu(\text{C}\equiv\text{O})$ stretching frequencies belonging to certain adsorption sites on oxide-supported Rh.^{15, 67, 68} The band at 2070–2030 cm^{-1} is due to CO adsorbed linearly to Rh^0 (depending on CO the coverage). Bridge-bonded CO ($\text{Rh}_2\text{—CO}$) exhibits a band at $\sim 1855 \text{ cm}^{-1}$ (not shown) and a pair of peaks at ~ 2100 and $\sim 2020 \text{ cm}^{-1}$ corresponds to the asymmetric and symmetric stretching of $\text{Rh}^+(\text{CO})_2$ (twin CO). These latter IR signals were detected when the oxide is covered by atomically dispersed Rh or when the crystallite size of Rh was very small.⁶⁷ The linear mode develops on bigger particles.

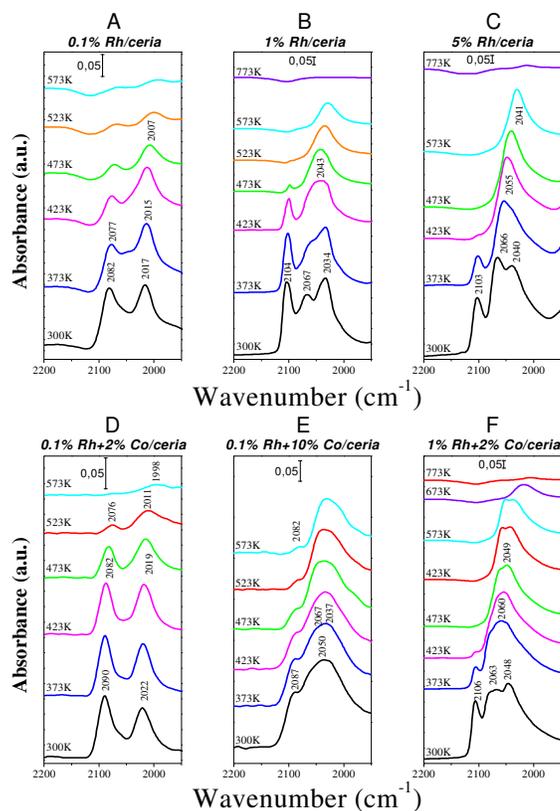


Fig. 4 DRIFT spectra after CO adsorption (at 300 K) followed by subsequent annealing at higher temperatures on (A) 0.1% Rh/ceria, (B) 1% Rh/ceria, (C) 5% Rh/ceria, (D) 0.1%Rh+2% Co/ceria, (E) 0.1% Rh+10% Co/ceria and (F) 1% Rh+2% Co/ceria.

The samples were reduced at 773 K prior to CO adsorption. The adsorption of CO was performed in a flow system using 10% CO in He at room temperature for 30 minutes. Afterward, the reactor was flushed with He for 30 minutes and the sample was heated in He flow with a heating rate of 20 K/min. Fig. 4A represents spectra obtained on 0.1% Rh/ceria. At 300 K, two bands with almost equal intensity were observed at 2082 and 2017 cm^{-1} , which can be attributed to a dicarbonyl Rh species associated with Rh^+ ions.^{15, 67, 69} A similar Rh twin dicarbonyl feature was obtained on Rh/alumina catalyst at very low metal content with high dispersity.⁶⁷ Upon increasing the temperature to 373 K, the intensity between the twin peaks, that is around 2050 cm^{-1} , increased, which is attributed to the development/increase of the linear species. At the same time, the twin peaks shifted to lower wavenumbers and lost intensity, in harmony with literature.^{69, 70} These changes occur in connection with the desorption of CO and the agglomeration of Rh particles. At 1% and 5% Rh content (Fig. 4B

and 3C, respectively), the FTIR spectra contain the bands of the dicarbonyl species and the linearly bonded CO mode at 2067 cm^{-1} at 300 K, indicating the presence of larger Rh crystallites already at this temperature. Upon annealing, the twin dicarbonyl form is transformed into the linear mode, which has higher thermal stability. It desorbs above 673 K.

Next, we discuss the influence of co-adsorbed Co. On the 0.1% Rh + 2% Co/ceria catalyst, similarly to the Co-free surface, the twin peaks of the Rh twin dicarbonyl species were detected at 300 K. The $\nu_{\text{as}}(\text{C}\equiv\text{O})$ peak at 2090 cm^{-1} was even sharper and less asymmetric than in the Co-free case, indicating the almost complete absence of linearly bonded CO. The DRIFT spectra were dominated by the twin feature also at higher temperatures, with stepwise decreasing intensities (Fig. 4D). In other words, 2% Co stabilized the small Rh particles when Rh was present in trace amounts. A different behavior was detected for 10% Co content (Fig. 4E), where already at 300 K, besides the small fraction of dicarbonyl species, a strong broad band appeared around 2050 cm^{-1} . Very probably, it is composed of (at least) two peaks (~ 2067 , $\sim 2037\text{ cm}^{-1}$), which are tentatively assigned to CO bound linearly to metallic Rh and Co, respectively. We note that in separate experiments on Rh-free Co-containing samples a very weak band appeared at 2037 cm^{-1} (not shown) that is attributed to CO bonded to a metallic fraction of cobalt, since CO cannot adsorb on oxidized Co at 300 K. The appearance of linearly bonded CO on Rh thus indicates that the higher Co loading induces some agglomeration of Rh for 0.1% Rh + 10% Co/ceria. For 1% Rh + 2% Co/ceria (Fig. 4F), the two adsorption modes of CO, linearly bonded to Rh (2063 cm^{-1}) and Co (2048 cm^{-1}) can be clearly distinguished. A different DRIFT feature was observed on the MgO supported Co-Rh bimetallic system.⁷¹ Only linearly bonded CO species was detected. The position of the linear CO band on Rh-Co/MgO was located between those on Rh/MgO and Co/MgO, and the linear CO band on Rh-Co/MgO was much broader than that of Rh/MgO. This may suggest the formation of well-mixed Rh-Co alloy, which was also verified by the Rh *K*- and Co *K*-edge EXAFS analysis.^{31, 72} In our ceria supported bimetallic system similar univoque conclusion could not be deduced from DRIFTS measurements. Although the strong broadening in the linear CO range – especially in the case of 0.1% Rh + 10% Co/ceria – may indicate a certain extent of alloy formation.

3.4 X-ray photoelectron spectroscopy

Fig. 5 shows the Rh 3d spectra of 0.1% Rh/ceria (A), 1% Rh/ceria (B) and of 5% Rh/ceria (C and D) after oxidation and reduction followed by stepwise heating in inert gas. After oxidation at 673 K, on all three samples the Rh $3d_{3/2}$ peak appeared at 309.2 eV and the Rh

$3d_{1/2}$ peak at 314.0 eV. After reduction at 773 K, the doublet markedly decreased in intensity and shifted to lower binding energies; the Rh $3d_{3/2}$ component at 307.1 eV indicates a metallic state. The drastic intensity decrease may be attributed to the agglomeration (sintering) and perhaps to some encapsulation of Rh particles by the ceria support. We note that the total amount of Rh did not change, as shown by our EDX measurements. The agglomeration of Rh is also evidenced by TEM images, which show an increase of the average size from 1.1 ± 0.45 nm before reduction to 3.9 ± 1.45 nm after reduction on 1% Rh/ceria. A similar drastic increase was obtained on 5% Rh/ceria, from 1.3 ± 0.3 to 4.7 ± 2.0 nm. The agglomeration is frequently attributed to Ostwald ripening; in this scenario, the mass transport is realized by the migration of individual atoms that are detached from the clusters. An alternative way would be coalescence by cluster migration, which was demonstrated by STM for small clusters (~ 10 atoms) on Pd/TiO₂(110) even at room temperature.⁷³ Encapsulation of Rh is well-documented on TiO₂(110) above 700 K, as shown by XPS, LEIS and STM.^{74, 75} Partial covering by ceria was observed recently on Rh-CeO₂/MgO system by DRIFTS method.⁷¹ Very recently, near ambient pressure X-ray photoelectron spectroscopy (nap-XPS) demonstrated that the strong metal support interaction effect (SMSI) found in the Ni-ceria system is associated with the decoration and burial of metallic particles by the partially reduced support.⁷⁶ We cannot exclude that this process occurs in the Rh-ceria system; however, since CO adsorption is not blocked after reduction (see DRIFTS results), encapsulation is probably very limited, if any, below 773 K.

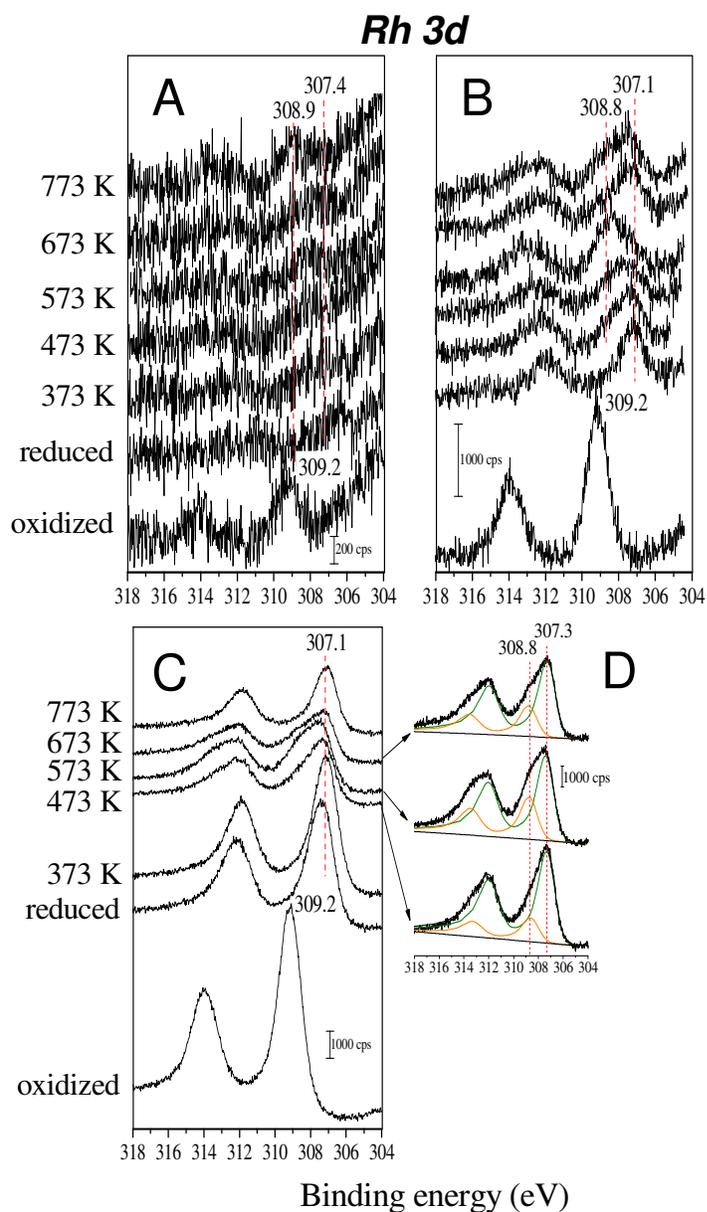


Fig. 5 Rh 3d XPS after oxidation (673 K), reduction (773 K) and subsequent heating in nitrogen atmosphere; (A) 0.1% Rh/ceria, (B) 1% Rh/ceria, (C) 5% Rh/ceria and (D) deconvoluted spectra of (C).

After reduction, the samples were heated in nitrogen atmosphere in the catalysis chamber from 300 to 773 K, and were held at that temperature for 2 min. Upon heating, we find a broadening of the Rh 3d feature for all Rh loadings, indicating the appearance of a new component at 308.8 eV (Fig. 5). The changes can be better analyzed for the higher Rh loadings of 1% and 5% Rh (5B and 5C), respectively, and some additional representative data

for lower metal content are included in Fig. S2. On the oxidized samples, the Rh 3d_{3/2} peak is observed at 309.2 eV, after reduction it shifted to 307.1 eV. Upon heating, a shoulder developed at 308.8 eV and reached maximum intensity at 573 K and then decreased again at higher temperatures. At 773 K the main peak was situated at 307.1 eV and a shoulder remained at 308.8 eV. In Fig. 5D, the spectra of the 5% Rh/ceria catalyst obtained at 473, 573 and 673 K (Fig. 5C) are deconvoluted, showing two well separated peaks at 307.3 and 308.8 eV.

Basically, we may consider two reasons for the upward shift of the Rh 3d peaks. One explanation could be an electronic interaction between Rh and ceria, which was observed between reduced titania and different metals including Rh.⁷⁷⁻⁸⁰ The presence of a high number of defects and oxygen vacancies in ceria or in titania could initiate an increased electron flow between the metal and the support. Recently, TiO₂(110) surfaces with Pt adatoms were examined using a noncontact atomic force microscope (NC-AFM) and Kelvin probe force microscope (KPFM). The observed work function decrease was attributed to an electric dipole moment directed toward the vacuum, as a result of electron transfer from the adatom to the TiO₂ substrate.^{81, 82} Similar phenomena may occur for the Rh-ceria system, forming partially positively charged Rh. The second possibility could be an oxygen transport from ceria to Rh, causing the observed shift in the Rh 3d spectra. Earlier, oxygen migration was supported by TPD and Auger spectroscopy for the Rh-ceria system^{83, 84}, and recently an STM study gave further evidence.⁸⁵ Moreover, Vayssilov et al.¹³ showed the coexistence of two different interaction mechanisms, a purely electronic effect involving electron transfer from Pt to CeO₂ and a second channel, involving transport of activated oxygen from nanostructured ceria to Pt, i.e. oxygen spillover. Both effects were experimentally detected using resonant photoelectron spectroscopy. In our case, the oxygen migration from ceria to Rh is detectable above 373 K in XPS (Fig. 5), and is most pronounced between 473-673 K. Interestingly, the oxygen spillover is partially reversible, as indicated by the dominance of the metallic Rh peak at 773 K. The easy formation of this Rh-O species and its stability-instability on ceria may be responsible for the strongly enhanced catalytic activity of Rh in several catalytic reactions.

In an alternative explanation of our XPS data, we may also suppose the formation of Rh-O-Ce and Rh-O-Rh bonds which were demonstrated by *in situ* quick scanning X-ray absorption fine structure (QXAFS) experiments earlier.⁸⁶ Oxidation and reduction of Rh species on Rh/CeO₂/SiO₂ catalyst were promoted by the presence of CeO₂ as indicated by the comparison of the profiles of the temperature-programmed oxidation (TPO) and reduction

(TPR) of Rh/CeO₂/SiO₂.⁸⁶ *In situ* QXAFS during the TPO and TPR indicated that the formation of the Rh-O-Ce bond was followed by that of Rh-O-Rh during the TPO.

From Fig. 6A, it is evident that the source of the oxygen is the ceria itself. We note here that the XP spectra of ceria is rather complex, it was analyzed after literature. A minor reduction of Ce⁴⁺ to Ce³⁺ is best detectable as the small intensity increase of the u' (903.9 eV) and v' (885.3 eV) peaks and also the weaker u⁰ (899.3 eV) and v⁰ (880.2 eV) components, which are characteristic of Ce³⁺.^{28, 29, 87-89} As Fig. 6A shows, the Ce³⁺/(Ce⁴⁺+Ce³⁺) ratio is higher on Rh/ceria system than on reduced ceria (compare bottom and center spectrum). Notably, the increase is smaller than expected. The reason is that above 373 K the diffusion of bulk oxygen to the surface is very quick as it was observed in a separate experiment shown in Fig. 6B. Therein, CeO₂ was first strongly reduced (Ce³⁺ signal indicated by a vertical arrow), and subsequently stepwise heated in vacuum; at each temperature the sample was kept for 2 min. The figure shows that above 473 K the ceria surface significantly re-oxidized with oxygen provided by the ceria bulk as reservoir.

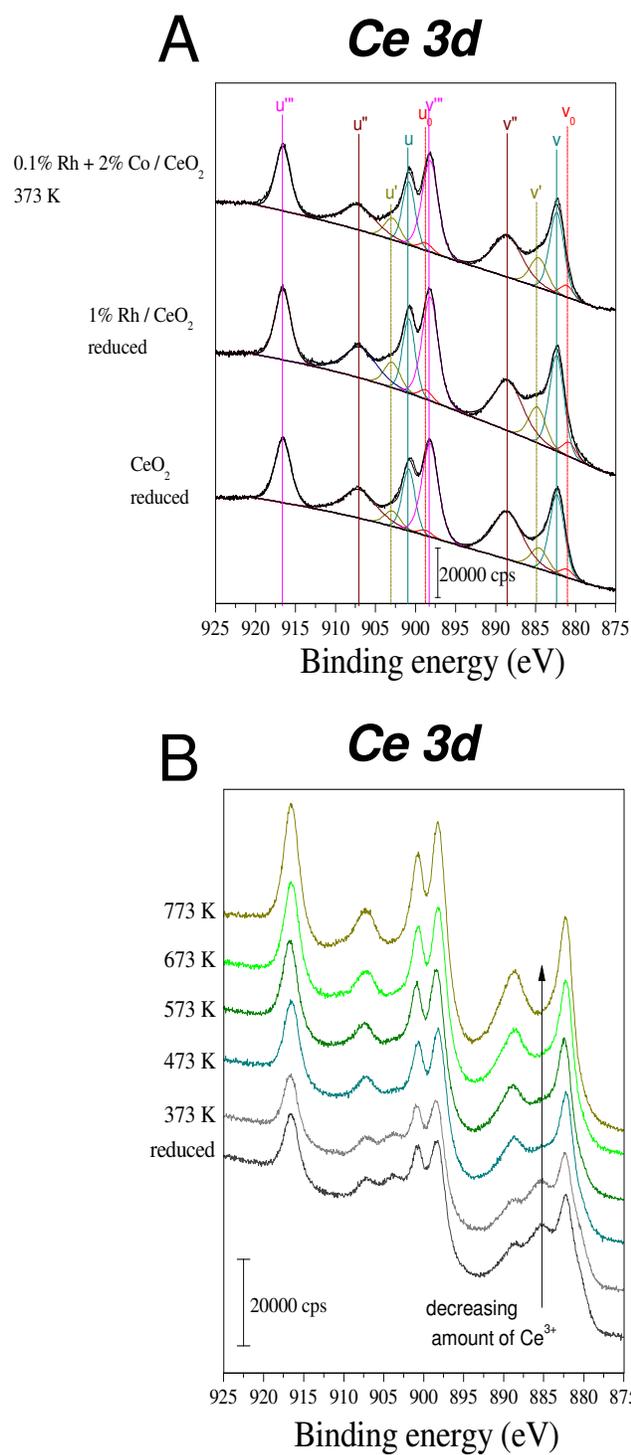


Fig. 6 Ce 3d XP spectra obtained on reduced ceria and Rh, Rh-Co containing ceria (A) Strongly reduced (at 773 K for 120 min) ceria heated in vacuum at different temperatures (B)

In Fig. 7 we display Co 2p_{3/2} spectra from the 2% Co/ceria and 10% Co/ceria samples. After oxidation at 673 K, the characteristic signal from Co₃O₄ appeared at 779.7 eV. Upon reduction at 773 K, the intensity of the Co peak decreased and only a small new peak characteristic of metallic Co developed at 777.8 eV; this indicates that Co is difficult to reduce at this temperature.^{21, 24, 28, 29} The overall intensity decrease may be attributed to the dissolution in ceria and encapsulation of cobalt clusters by the support. Agglomeration or coalescence did not play a significant role, because the Co XP peaks gained intensity when the sample temperature was increased in stepwise manner after evacuation in nitrogen atmosphere (Fig. 7A and B). The other remarkable change during the heat treatment is the disappearance of the metallic Co peak at 777.8 eV above 473 K, marking the significant oxidation of cobalt to Co²⁺. Although the Co 2p_{3/2} peak positions of CoO and Co₃O₄ are almost the same, the presence of CoO (Co²⁺) is indicated by the characteristic satellite at higher binding energies (compare top and bottom spectrum in Fig. 7B) and the spin-orbit splitting of 16.0 eV. This high value is typical for paramagnetic Co²⁺ compounds due to multiplet splitting. After oxidation (Fig. 7B upper spectrum), the separation was only 15.2 eV close to the values on diamagnetic Co compounds like Co³⁺ complexes.^{90, 91} Peak fittings of some Co 2p spectra are depicted in Fig. S2. In the Co-ceria system, the decrease of Co XPS signal upon hydrogen reduction is attributed to the encapsulation by ceria as was also found for the Ni/ceria system.⁷⁶ It is interesting that this process is reversible, which is concluded from the fact that CoO is recovered above 473 K. In this sense, the Co/ceria system is close to the Ni/ceria catalyst, where the hydrogen-induced burial (encapsulation) and dig out of Ni is a reversible process.⁷⁶

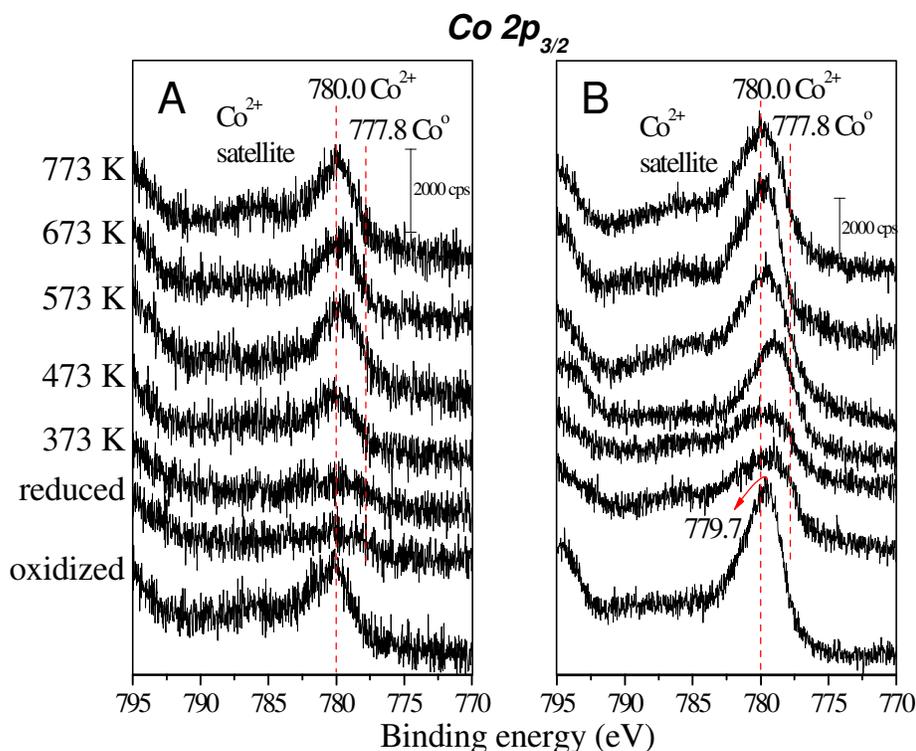


Fig. 7 Co 2p_{3/2} XPS spectra obtained on 2% Co/ceria (A) and 10% Co/ceria catalysts (A) after oxidation and reduction and subsequent heating under inert gas.

The spectra of the monometallic Rh-ceria or Co-ceria systems were significantly altered in the presence of the second metal. Fig. 8 displays the Rh 3d and Co 2p_{3/2} spectra obtained after oxidation/reduction and subsequent heat treatment at different temperatures for the 0.1% Rh + 2% Co/ceria and 0.1% Rh + 10% Co/ceria catalysts. When comparing the Rh 3d signals of the monometallic 0.1% Rh system (Fig. 5A) and the bimetallic Rh-Co systems (Fig. 8A and B), the first important observation is the significantly higher intensity for the latter. This behavior indicates that a larger fraction of Rh is accessible for XPS even after reduction, due to a suppression of agglomeration or encapsulation in the presence of Co adatoms. Notably, this was concluded from the DRIFTS measurement, too (Fig. 4A, Fig. 4D). The inhibited agglomeration of Rh in the presence of Co is also clearly evident from the HRTEM images for 1% Rh + 2% Co/ceria before and after reduction. The particles sizes did not alter after reduction at 773 K. 1.5 ± 0.5 nm was measured before reduction and 1.7 ± 0.6 nm was obtained after reduction. Very similar data was obtained for 1% Rh + 10% Co/ceria. For comparison we mention again that the reduction of monometallic 1% Rh/ceria resulted in 2.4-6.5 nm particle sizes. Fig. 3E and F represent HRTEM images of reduced bimetallic systems showing the inhibiting effect of Co on Rh agglomeration.

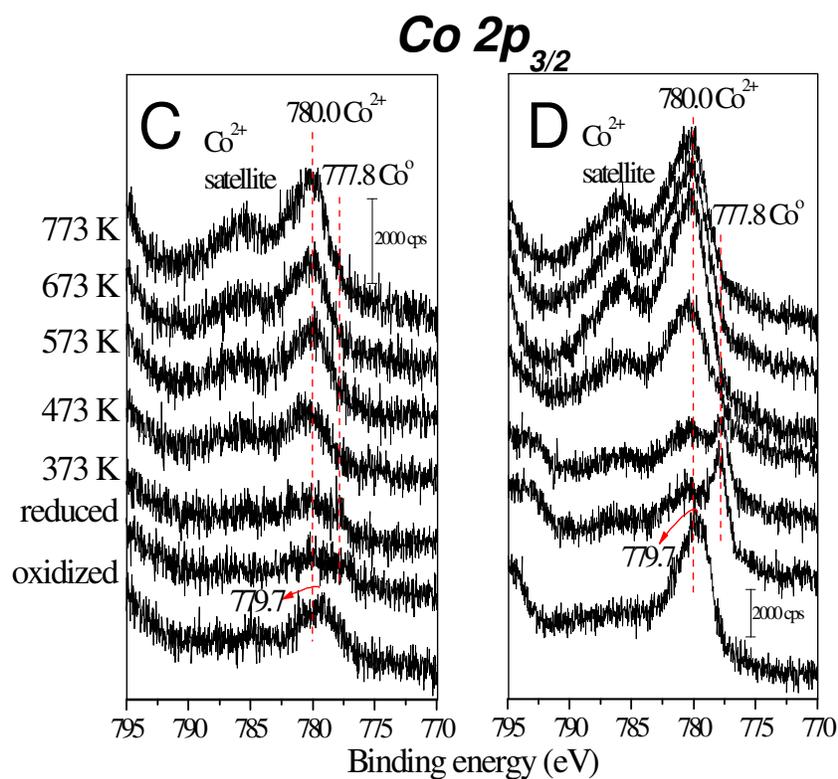
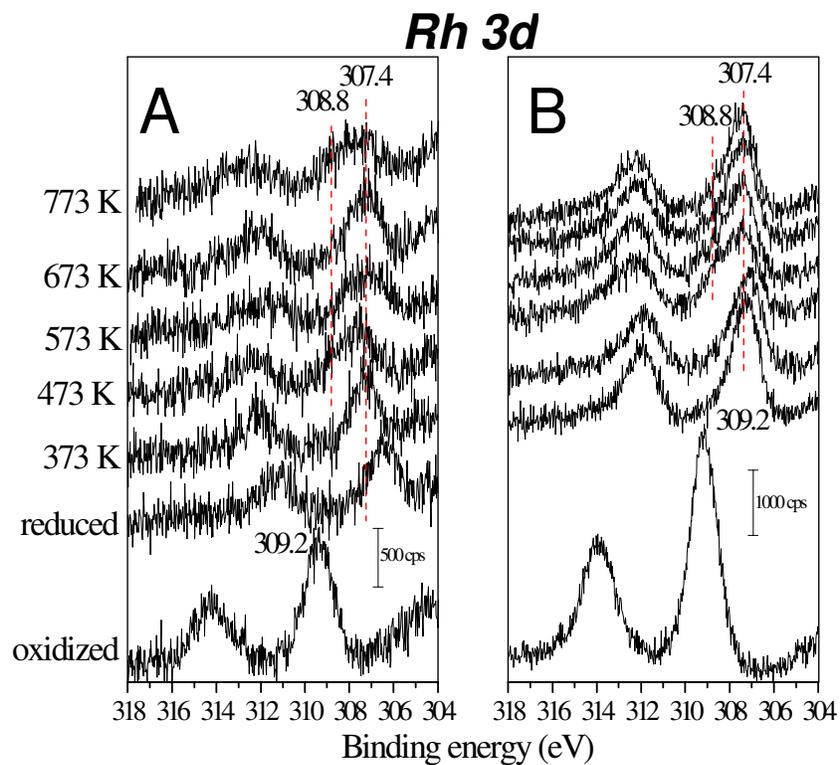


Fig. 8 Rh 3d XP spectra obtained on Rh-Co bimetallic catalysts; 0.1% Rh + 2% Co/ceria (A), 0.1% Rh + 10% Co/ceria (B), Co 2p_{3/2} XP spectra obtained on Rh-Co bimetallic catalysts; 0.1% Rh + 2% Co/ceria (C), 0.1% Rh + 10% Co/ceria (D)

Based on the XRD, TEM and DRIFTS results, we should distinguish between the 2 and 10% Co-containing catalysts in the interpretation of XPS results for the bimetallic Rh-Co system. As presented above, 2 and 10% Co loading results in a drastic increase of the ceria dispersion; this effect is much more pronounced at 10% Co loading (Fig. 2A and Fig. 3C and D). Our DRIFTS results (Fig. 4D) demonstrated that 2% Co stabilizes a higher dispersion of Rh, and 10% Co increases the formation of larger particles; nevertheless, the significant intensity from twin-dicarbonyl species after CO adsorption indicates that nearly atomically dispersed Rh is still present up to 473-523 K. We therefore conclude that Rh agglomeration is probably hindered in the bimetallic system at low Co content of 2%, but slightly occurs at the higher content of 10% Co.

Another significant observation is that for the bimetallic Rh-Co system, the Rh 3d peak at ~308.8 eV due to oxygen migration above 300 K is less pronounced than for the monometallic system (compare Fig. 5. and Fig. 8A and B). This indicates that such kind of oxygen transport occurs in the bimetallic system, but to a lesser extent than for the monometallic case. It also seems that Co delays the oxygen migration from ceria to Rh.

Figures 7C and D display the Co 2p_{3/2} region after reduction and following heat treatment. It is remarkable that mainly at 10% Co content the presence of Rh significantly assisted the reduction of Co²⁺ to Co⁰, as was experienced in our previous work.²⁹ Upon thermal treatment, the Co 2p_{3/2} moved to higher binding energy from 777.8 eV to 780.0 eV indicating the re-oxidation of metallic Co. Above 473 K, the re-oxidation to mainly Co²⁺ is completed (Fig. 8A and B). As it can be seen in Fig. 6A, the ceria is in slightly reduced state in the bimetallic system, too. It is very important to note that compared to the monometallic Rh sample, the oxygen migration from ceria to Rh is less pronounced in the presence of Co adatom. In the bimetallic system, the Co oxidation by ceria is faster than the oxygen migration from ceria to Rh. Highly dispersed metallic Rh can facilitate the reduction of Co²⁺ and the formed metallic Co can be rapidly re-oxidized by the ceria.

3.5 Low-energy ion scattering (LEIS) experiments

As LEIS is widely used to determine the outermost surface composition⁹² we also tried to map

the top layer of the Rh/ceria system. This method was successfully applied in our previous studies even for porous materials (titania-supported Au and Rh).⁵² In spite of this fact, unfortunately, this method sometimes is far from straightforward. In certain cases, neutralization effects can be too strong. This enhanced neutralization was experienced for Ce/Rh(111)⁹³ and to a certain extent on Ce/Cu(111), when Ne⁺ was used.⁵⁸ In our extended LEIS experiments on Rh/ceria system Rh signal was not detected. We suppose that a strong neutralization effect could be the reason for the lack of Rh signals in LEIS in the present cases, although we have learnt from DRIFTS experiments using CO adsorption that certain amount of Rh should exist on the surface. Rh LEIS signal was not detected even after prolonged etching with 4 keV ions.

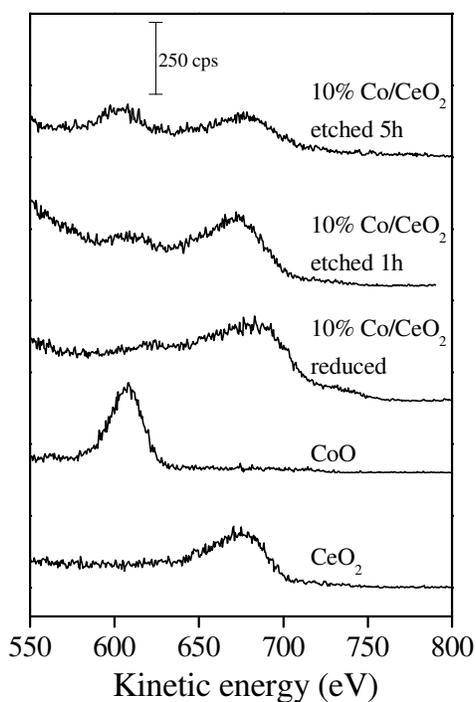


Fig. 9 LEIS spectra of reduced ceria, clean CoO standard, reduced 10% Co/ceria and etched Co/ceria obtained with 800 eV He⁺.

Next, we studied the surface composition of the Co/ceria system with LEIS technique applying 800 eV He⁺ ions (Fig. 9). For comparison, we display a LEIS spectrum of a clean CoO standard. After reduction of 10% Co/ceria, the Co signal was very weak. The almost complete lack of the Co signal can be explained mostly by the penetration or dissolution of cobalt into the ceria and to a lesser extent by encapsulation by ceria. A similar conclusion was

drawn from XRD and XPS experiments (see above). Our recent XPS and LEIS work on a Co/CeO₂(111) model catalyst demonstrated that Co²⁺ penetration into the ceria layer was significant and that for metallic Co presumably agglomeration occurs.³⁹ It was verified that no disturbing neutralization effects occur for the Co peaks in LEIS using He⁺ or Ne⁺ projectiles; however, since strong matrix effects are found for the O peak with He⁺, this peak was not used for quantitative analysis.

If encapsulation or dissolution phenomena would be the main cause of the lack of Co signal in Co/ceria catalysts, we should detect a Co signal after prolonged Ar⁺ or Ne⁺ ion bombardment. As Fig. 9 demonstrates, Co indeed showed up, with its intensity increasing with etching time.

4. SUMMARY AND CONCLUSIONS

We investigated CeO₂-supported Rh, Co and bimetallic Rh-Co catalytic materials using XRD, HRTEM, DRIFTS, XPS and LEIS. Our studies concentrated mainly on the reduced materials, which successfully operate under real catalytic conditions.

1. At small Rh loading (0.1%), Rh is in very dispersed state on ceria, while at higher Rh loadings (1-5%), Rh forms 2-8 nm particles. HRTEM and XPS showed significant agglomeration at high temperature (773 K). DRIFTS using CO adsorption showed that the encapsulation does not fully occur, and some atomically dispersed Rh may exist even after high temperature reduction.
2. On reduced Rh/ceria, oxygen transfer from ceria to Rh and possibly also electron transfer from Rh to ceria take place, according to XPS. Oxygen transport from ceria to Rh is well-detectable between 473 and 673 K.
3. XRD and HRTEM revealed that loading with Co induces the formation of smaller ceria crystallites; for 10% Co/ceria, the CeO₂ particle size decreased from 27.6 to 10.7 nm. Co is almost completely oxidized to Co²⁺.
4. Strong dissolution of Co into ceria and a certain extent of Co encapsulation by ceria were experienced by XRD, XPS and LEIS.
5. The presence of Rh adatoms enhances the reduction of cobalt. During thermal treatment, re-oxidation of Co takes place in the bimetallic system. The Rh agglomeration and oxygen

migration from ceria to Rh are hindered by the presence of cobalt. Ceria is in a slightly reduced state on Rh/ceria, Co/ceria and on the bimetallic materials.

Author information

Corresponding Author

*E-mail: jkiss@chem.u-szeged.hu

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Notes

The authors declare no competing financial interest.

Acknowledgement

This work was supported by the Alexander von Humboldt Foundation within the Research Group Linkage Program, by COST Action CM1104, and by the Cluster of Excellence ‘‘Engineering of Advanced Materials’’.

- 1 G. W. Huber, S. Iborra and A. Corma, *Chem. Rev.*, 2006, **106**, 4044-4098.
- 2 M. Balat, *Int. J. Hydrogen Energy*, 2008, **33**, 4013-4029.
- 3 D. Chen and L. He, *ChemCatChem*, 2011, **3**, 490-511.
- 4 L. F. Brown, *Int. J. Hydrogen Energy*, 2001, **26**, 381-397.
- 5 A. Haryanto, S. Fernando, N. Murali and S. Adhikari, *Energy Fuels*, 2005, **19**, 2098-2106.
- 6 R. D. Cortright, R. R. Davda and J. A. Dumesic, *Nature*, 2002, **418**, 964-967.
- 7 Y. Lykhach, A. Neitzel, K. Sevciková, V. Johánek, N. Tsud, T. Skála, K. C. Prince, V. Matolin and J. Libuda, *ChemSusChem*, 2014, **7**, 77-81.

- 8 A. Trovarelli and P. Fomasiero, *Catalysis by Ceria and Related Materials*, 2nd ed., Imperial College Press, London, 2013.
- 9 S. D. Park, J. M. Vohs and R. J. Gorte, *Nature*, 2000, **404**, 265-267.
- 10 G. A. Deluga, J. R. Salge, L. D. Schmidt and X. E. Verykios, *Science*, 2004, **303**, 993-997.
- 11 C. T. Campbell and C. H. F. Peden, *Science*, 2005, **309**, 713-714.
- 12 L. V. Mattos, G. Jacobs, B. H. Davis and F. B. Noronha, *Chem. Rev.*, 2012, **112**, 4094-4123.
- 13 G. N. Vayssilov, Y. Lykhach, A. Migani, T. Staudt, G. P. Petrova, N. Tsud, T. Skála, F. Bruix, F. Illas, K. C. Prince, V. Matolin, K. M. Neyman and J. Libuda, *J. Nat. Mater.*, 2011, **10**, 310-315.
- 14 M. Mavriakis and M. A. Barteau, *J. Mol. Catal. A*, 1998, **131**, 135-147.
- 15 A. Yee, S. J. Morrison and H. Idriss, *Catal. Today*, 2000, **63**, 327-335.
- 16 A. Erdőhelyi, J. Raskó, T. Kecskés, M. Tóth, M. Dömök and K. Báán, *Catal. Today*, 2006, **116**, 367-376.
- 17 J. Llorca, N. Homs, J. Sales and P. R. de la Piscina, *J. Catal.*, 2002, **209**, 306-317.
- 18 S. S. Y. Lin, D. H. Kim and S. Y. Ha, *Catal. Lett.*, 2008, **122**, 295-301.
- 19 J. Llorca, N. Homs and P. R. de la Piscina, *J. Catal.*, 2004, **227**, 556-560.
- 20 E. Martono, M. P. Hyman and J. M. Vohs, *Phys. Chem. Chem. Phys.*, 2011, **13**, 9880-9886.
- 21 E. Martono and J. M. Vohs, *J. Catal.*, 2012, **291**, 79-86.
- 22 M. S. Batista, R. K. S. Santos, E. M. Assaf, J. M. Assaf and E. A. Ticinalli, *J. Power Sources*, 2003, **124**, 99-103.
- 23 J. Kaspar, P. Fornasiero and M. Graziani, *Catal. Today*, 1999, **50**, 285-298.
- 24 H. Song and U. S. Ozkan, *J. Mol. Catal. A*, 2010, **318**, 21-29.
- 25 B. Bayram, I. I. Soykal, D. Deak, J. T. Miller and U. S. Ozkan, *J. Catal.*, 2011, **284**, 77-89.
- 26 I. I. Soykal, H. Sohn and U. S. Ozkan, *ACS Catal.*, 2012, **2**, 2335-2348.
- 27 A. M. da Silva, K. R. Souza, L. V. Mattos, G. Jacobs, B. H. Davis and F. B. Noronha, *Catal. Today*, 2011, **164**, 234-239.
- 28 L. Óvári, S. Krick Calderon, Y. Lykhach, J. Libuda, A. Erdőhelyi, C. Papp, J. Kiss and H.-P. Steinrück, *J. Catal.*, 2013, **307**, 132-139.

- 29 Zs. Ferencz, A. Erdőhelyi, K. Baán, A. Oszkó, L. Óvári, Z. Kónya, C. Papp, H.-P. Steinrück and J. Kiss, *ACS Catal.*, 2014, **4**, 1205-1218.
- 30 E. Varga, Zs. Ferencz, A. Oszkó, A. Erdőhelyi and J. Kiss, *J. Mol. Catal. A*, 2015, **397**, 127-133.
- 31 S. Naito, H. Tanaka, S. Kado, M. Toshihiro, S. Naito, K. Okumura, K. Kunimori and K. Tomishige, *J. Catal.*, 2008, **259**, 138-146.
- 32 H. Tanaka, R. Kaino, Y. Nakagawa and K. Tomishige, *Appl. Catal. A*, 2010, **378**, 187-194.
- 33 Y. Mukainakano, B. Li, S. Kado, T. Miyazawa, K. Okumura, T. Miyao, S. Naito, K. Kumimori and K. Tomishige, *Appl. Catal. A*, 2007, **318**, 252-264.
- 34 Y. Mukainakano, K. Yoshida, K. Okumura, K. Kumimori and K. Tomishige, *Catal. Today*, 2008, **132**, 101-108.
- 35 D. Li, Y. Nakagawa and K. Tomishige, *Appl. Catal. A*, 2011, **408**, 1-24.
- 36 Zs. Ferencz, K. Baán, A. Oszkó, Z. Kónya, T. Kecskés and A. Erdőhelyi, *Catal. Today*, 2014, **228**, 123-130.
- 37 I. I. Soykal, H. Sohn, D. Singh, J. T. Miller and U. S. Ozkan, *ACS Catal.*, 2014, **4**, 585-592.
- 38 S. H. Overbury, D. R. Mullins and L. Kundakovich, *Surf. Sci.*, 2001, **470**, 243-254.
- 39 G. Vári, L. Óvári, J. Kiss, C. Papp, H.-P. Steinrück and Z. Kónya, *J. Phys. Chem. C*, 2015, **119**, 9324-9333.
- 40 K. M. Cook, S. Poudyal, J. T. Miller, C. Bartholomew and W. C. Hecker, *Appl. Catal. A*, 2012, **449**, 69-80.
- 41 G. Jacobs, Y. Ji, B. H. Davis, D. Cronauer, A. J. Kropf and C. L. Marshall, *Appl. Catal. A*, 2007, **333**, 177-191.
- 42 D. Kulkarni and I. E. Wachs, *Appl. Catal. A*, 2002, **237**, 121-137.
- 43 F. B. Noronha, A. Frydman, D. A. G. Aranda, C. Perez, R. R. Soares, B. Morawek, D. Castner, C. T. Campbell, R. Frety and M. Schmal, *Catal. Today*, 1996, **28**, 147-157.
- 44 L. Guzzi, G. Boskovic and E. Kiss, *Catal. Rev.*, 2010, **52**, 133-203.
- 45 J. A. Rodriguez, *Surf. Sci. Rep.*, 1966, **24**, 223-287.
- 46 Z. Wang, F. Yang, S. Axnanda, C. Liu and D. W. Goodman, *Appl. Catal. A*, 2011, **391**, 342-349.
- 47 L. Bugyi, A. Berkó, L. Óvári, A. M. Kiss and J. Kiss, *Surf. Sci.*, 2008, **602**, 1650-1658.

- 48 J. B. Park, S. F. Conner and D. A. Chen, *J. Phys. Chem. C*, 2008, **112**, 5490-5497.
- 49 L. Óvári, L. Bugyi, Z. Majzik, A. Berkó and J. Kiss, *J. Chem. Phys. C*, 2008, **112**, 18011-18016.
- 50 L. Bugyi, L. Óvári and J. Kiss, *Surf. Sci.*, 2009, **603**, 2958-2963.
- 51 H. L. Abbott, A. Aumer, Y. Lei, C. Asokan, R. J. Meyer, M. Sterrer, S. Shaiklutdinov and H.-J. Freund, *J. Phys. Chem. C*, 2010, **114**, 17099-17104.
- 52 J. Kiss, L. Óvári, A. Oszkó, G. Pótári, M. Tóth, K. Baán and A. Erdőhelyi, *Catal. Today*, 2012, **181**, 163-170.
- 53 F. Gao, Y. Wang and D. W. Goodman, *J. Phys. Chem. C*, 2010, **114**, 4036-4043.
- 54 L. Óvári, A. Berkó, N. Balázs, Z. Majzik and J. Kiss, *Langmuir*, 2010, **26**, 2167-2175.
- 55 S. A. Tenny, J. S. Ratliff, C. C. Roberts, W. He, S. C. Ammal, A. Heyden and D. A. Chen, *J. Phys. Chem. C*, 2010, **114**, 21652-21663.
- 56 W. F. Egelhoff Jr, *Surf. Sci. Rep.*, 1987, **6**, 253-415.
- 57 C. Papp and H.-P. Steinrück, *Surf. Sci. Rep.*, 2013, **68**, 446-487.
- 58 G. Vári, L. Óvári, C. Papp, H.-P. Steinrück, J. Kiss and Z. Kónya, *Phys. Chem. Chem. Phys.*, 2015, **17**, 5124-5132.
- 59 H. H. Brongersma, H. Draxler and M. B. de Ridder P., *Surf. Sci. Rep.*, 2007, **62**, 63-109.
- 60 A. Trovarelli, *Catal. Rev.*, 1996, **38**, 349-520.
- 61 H. C. Yao and Y. C. Yu Yao, *J. Catal.*, 1984, **86**, 254-265.
- 62 F. Sadi, D. Duprez, F. Gérard and A. Miloudi, *J. Catal.*, 2003, **213**, 226-234.
- 63 S. W. Yu, H. H. Huang, C. W. Tang and C. B. Wang, *Int. J. Hydrogen Energy*, 2014, **39**, 20700-20711.
- 64 F. Esch, S. Fabris, L. Zhou, T. Montini, C. Africh, P. Fornasiero, G. Comelli and R. Rosei, *Science*, 2005, **309**, 752-755.
- 65 P. Y. Sheng, W. W. Chiu, A. Yee, S. J. Morrison and H. Idriss, *Cat. Today*, 2007, **129**, 313-321.
- 66 A. M. da Silva, K. R. de Souza, G. Jacobs, U. M. Graham, B. H. Davis, L. V. Mattos and F. V. Noronha, *Appl. Catal. B*, 2011, **102**, 94-109.
- 67 F. Solymosi and M. Pásztor, *J. Phys. Chem.*, 1985, **89**, 4789-4793.

- 68 J. T. Yates Jr, T. M. Duncan, S. D. Worley and R. W. Vaughan, *J. Chem. Phys.*, 1979, **70**, 1219-1224.
- 69 D. A. Bulushev and G. F. Froment, *J. Mol. Catal. A*, 1999, **139**, 63-72.
- 70 R. Dictor and S. Roberts, *J. Phys. Chem.*, 1989, **93**, 2526-2532.
- 71 D. Li, S. Sakai and Nakagawa, Y., Tomishige, K., *Phys. Chem. Chem. Phys.*, 2012, **14**, 9204-9213.
- 72 H. Tanaka, R. Kaino, K. Okumura, T. Kizuka, Y. Nakagawa and K. Tomishige, *Appl. Catal. A*, 2010, **378**, 175-186.
- 73 M. J. J. Jak, C. Konstapel, A. van Kreuningen, J. Verhoven and J. W. M. Frenken, *Surf. Sci.*, 2000, **475**, 295-310.
- 74 A. Berkó, G. Ménesi and F. Solymosi, *Surf. Sci.*, 1997, **372**, 202-210.
- 75 L. Óvári and J. Kiss, *Appl. Surf. Sci.*, 2006, **252**, 8624-8629.
- 76 A. Caballero, J. P. Holgado, V. M. Gonzales-delaCruz, S. E. Habas, T. Herranz and H. Salmeron, *Chem. Com.*, 2010, **46**, 1097-1099.
- 77 F. Solymosi, *Catal. Rev.*, 1968, **1**, 233-255.
- 78 M. A. Vannice and R. L. Garten, *J. Catal.*, 1979, **56**, 236-248.
- 79 F. Solymosi, A. Erdőhelyi and T. Bánsági, *J. Catal.*, 1981, **68**, 371-382.
- 80 G. Pótári, D. Madarász, L. Nagy, B. László, A. Sápi, A. Oszkó, Á Kukovecz, A. Erdőhelyi, Z. Kónya and J. Kiss, *Langmuir*, 2013, **29**, 3061-3072.
- 81 A. Sasahara, C. L. Pang and H. Onishi, *J. Phys. Chem. B*, 2006, **110**, 13453-13457.
- 82 A. Sasahara, C. L. Pang and H. Onishi, *J. Phys. Chem. B*, 2006, **110**, 17584-17588.
- 83 G. S. Zafiris and R. J. Gorte, *J. Catal.*, 1993, **139**, 561-567.
- 84 J. Stubenrauch and J. M. Vohs, *J. Catal.*, 1996, **159**, 50-57.
- 85 J. Zhou, P. Baddorf, D. R. Mullins and S. H. Overbury, *J. Phys. Chem.*, 2008, **112**, 9336-9345.
- 86 T. Miyazawa, K. Okumura, K. Kumimori and K. Tomishige, *J. Phys. Chem. C*, 2008, **112**, 2574-2583.
- 87 G. Praline, B. E. Koel, R. L. Hance, H. I. Lee and J. M. White, *J. Electron Spectr. and Related Phenom.*, 1980, **21**, 17-30.
- 88 A. Pfau and K. D. Schierbaum, *Surf. Sci.*, 1994, **321**, 71-80.

- 89 C. J. Nelin, P. S. Bagus, E. S. Ilton, S. A. Chambers, H. Kuhlenbeck and H.-J. Freund, *J. Quant. Chem.*, 2010, **110**, 2752-2764.
- 90 M. Schmid, A. Kaftan, H.-P. Steinrück and J. M. Gottfried, *Surf. Sci.*, 2012, **606**, 945-949.
- 91 C. D. Frost, C. A. McDowell and I. S. Woolsey, *Chem. Phys. Lett.*, 1972, **17**, 320-323.
- 92 H. Niehus and R. Spitzl, *Surf. Interface Anal.*, 1991, **17**, 287-307.
- 93 E. Napetschnig, M. Schmid and P. Varga, *Surf. Sci.*, 2004, **556**, 1-10.

Legend of Tables:

Table 1. Some Physical Parameters of Bare Supports and Co and Rh Loaded Catalyst

Legend of Figures:

Fig. 1 Ethanol conversion and hydrogen selectivity in the EtOH + H₂O (1:3) reaction at 723 K on Co- and Rh-containing ceria based catalysts. Data are plotted at 120 min reaction time.

Fig. 2 XRD pattern of different ceria and ceria supported Rh, Co and Rh-Co catalysts

Fig. 3 TEM images of ceria and ceria supported Rh, Co and Rh-Co catalysts

Fig. 4 DRIFT spectra after CO adsorption (at 300 K) followed by subsequent annealing at higher temperatures on (A) 0.1% Rh/ceria, (B) 1% Rh/ceria, (C) 5% Rh/ceria, (D) 0.1% Rh+2% Co/ceria, (E) 0.1% Rh+10% Co/ceria and (F) 1% Rh+2% Co/ceria

Fig. 5 Rh 3d XPS after oxidation (673 K) and reduction (773 K) and subsequent heating in

nitrogen atmosphere; (A) 0.1% Rh/ceria, (B) 1% Rh/ceria, (C) 5% Rh/ceria and (D) deconvoluted spectra of (C)

Fig. 6 Ce 3d XP spectra obtained on reduced ceria and Rh, Rh-Co containing ceria (A) Strongly reduced (at 773 K for 120 min) ceria heated in vacuum at different temperatures (B)

Fig. 7 Co 2p_{3/2} XP spectra obtained on 2% Co/ceria (A) and 10% Co/ceria catalysts (A) after oxidation and reduction and subsequent heating under inert gas

Fig. 8 Rh 3d XP spectra obtained on Rh-Co bimetallic catalysts; 0.1% Rh + 2% Co/ceria (A), 0.1% Rh + 10% Co/ceria (B), Co 2p_{3/2} XP spectra obtained on Rh-Co bimetallic catalysts; 0.1% Rh + 2% Co/ceria (C), 0.1% Rh + 10% Co/ceria (D)

Fig. 9 (A) LEIS spectra obtained with 800 eV Ne⁺ projectiles taken of reduced ceria, clean Rh(111), reduced 5% Rh/ceria and etched Rh/ceria. (B) LEIS spectra of reduced ceria, clean CoO standard, reduced 10% Co/ceria and etched Co/ceria obtained with 800 eV He⁺

Figure S1. Survey spectra of 5% Rh/ceria in the as received state (A) and after reduction at 773 K for 1 h (B), as well as the same spectra of 0.1% Rh+10% Co/ceria (C,D), respectively

Figure S2. Deconvoluted Rh 3d spectra of 1% Rh/ceria (A) and Co 2p spectra of 10% Co/ceria (B) after oxidation, reduction and heating in N₂ up to 673 or 773 K.

