


# Green Chemistry

Accepted Manuscript

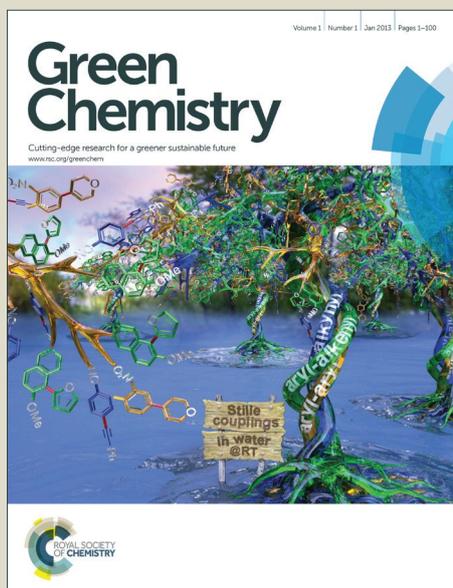

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



[www.rsc.org/greenchem](http://www.rsc.org/greenchem)

## ARTICLE

## Recovery of scandium from leachates of Greek bauxite residue by adsorption on functionalized chitosan-silica hybrid materials

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Joris Roosen,<sup>a,c</sup> Stijn Van Rosendael,<sup>a</sup> Chenna Rao Borra,<sup>b</sup> Tom Van Gerven,<sup>b</sup>  
Steven Mullens,<sup>c</sup> and Koen Binnemans\*<sup>a</sup>

Bauxite residue (red mud) is a waste residue that results from the production of alumina by the Bayer process. Since it finds no large-scale industrial application, it is stockpiled in large reservoirs. Nevertheless, it should be considered as a valuable secondary resource as it contains relatively large concentrations of critical metals like the rare earths, scandium being the most important one. In this work, we investigated the recovery of scandium from real leachates of Greek bauxite residue. In the separation of scandium from the other elements, the highest challenge arised from the chemical similarities between scandium(III) and iron(III). This hampers high selectivity for scandium, especially because iron, as one of the major elements in bauxite residue, is present in much higher concentrations than scandium. In order to achieve selectivity for scandium, chitosan-silica particles were functionalized with the chelating ligands diethylenetriamine pentaacetic acid (DTPA) and ethyleneglycol tetraacetic acid (EGTA). Both organic ligands were chosen because of the high stability constants between scandium(III) and the corresponding functional groups. The adsorption kinetics and the influence of pH on hydrolysis and adsorption were investigated batchwise from single-element solutions of scandium(III) and iron(III). In binary solutions of scandium(III) and iron(III), it was observed that only EGTA-functionalized chitosan-silica appeared to be highly selective for scandium(III) in favour of iron(III). EGTA-chitosan-silica shows a much higher selectivity over the state-of-the-art adsorbents for the separation of scandium(III) from iron(III). The latter material was therefore used as resin material in a column chromatography set-up in order to effectively separate scandium from the bauxite residue. The pure separation was achieved by eluting the column with a HNO<sub>3</sub> solution at pH 0.50, at which pH all other elements had already eluted.

### Introduction

Recovery of valuable metals from (industrial process) residues would be beneficial for both economical and sustainability reasons.<sup>1-5</sup> Especially the winning of rare-earth elements from secondary resources has gained interest as an additional route to their primary mining, since rare-earth elements have become indispensable in many modern high-tech and green applications.<sup>1, 6, 7</sup> Bauxite residue, also called “red mud”, is the waste product of the production of alumina from bauxite by the Bayer process.<sup>8</sup> Bauxite residue is stockpiled in huge amounts, but it is harmful, mainly due to its high alkalinity (pH ≥ 12).<sup>9-11</sup> Besides its major components (iron oxides, quartz, sodium aluminosilicates, calcium carbonate/aluminate and titanium dioxide), bauxite residue also contains valuable minor elements, such as the rare earths. The concentrations of these metals are low, but with a production rate of 120 million tons

per year, bauxite residue can be considered as an important candidate for valorization.<sup>1</sup> Moreover, compared to average concentration levels in the earth's crust, bauxite residue is especially enriched in scandium. Scandium is mainly used in Al-Sc alloys, resulting in superior properties, such as light weight, high strength, good thermal resistance and long durability.<sup>12</sup> Another important application includes the solid oxide fuel cells in which scandia-stabilized zirconia shows extremely high oxygen-ion conductivity for use as a highly efficient electrolyte.<sup>13</sup>

To recover scandium and other rare earths from the bauxite residue, they must be dissolved by leaching with inorganic acids. This is extensively investigated.<sup>14-17</sup> As a consequence of the high liquid-to-solid ratios generally used to obtain good recovery, the resulting leachate solutions contain low concentrations of scandium.<sup>14</sup> The most suitable technique for

concentration of very diluted scandium is therefore ion-exchange adsorption, which makes it possible to selectively recover scandium from the leachate by using proper types of ion-exchange resins, chelating resins, or varying desorption conditions.<sup>15</sup> Previous work showed that chitosan is the perfect material for the recovery of metal ions from diluted solutions by ion-exchange adsorption.<sup>18, 19</sup> Chitosan is a linear polysaccharide which is mainly obtained by alkaline deacetylation of chitin, a naturally abundant material that can be found in the exo-skeleton of crustacea (such as lobsters and shrimps) and insects.<sup>20-22</sup> Its low cost, abundant availability, biocompatibility, biodegradability, non-toxicity, and convenient modification possibilities (both physically and chemically) make chitosan an interesting material for various applications, including recovery of metals from aqueous solutions.<sup>20-25</sup> Chitosan shows excellent adsorption characteristics because of its high hydrophilicity (hydroxyl groups), high activity for the chelation of metal ions (primary amino groups), and a flexible structure which enables to adopt the suitable configuration for complexation with metal ions.<sup>26</sup> The large number of highly reactive amino and hydroxyl groups allows for convenient modifications of the structure. In this way, the selectivity for specifically targeted metal ions can be adjusted by immobilization of the proper functional group.<sup>26, 27</sup> Since pure chitosan suffers from poor mechanical properties and low porosity, it can be hybridized with silica to obtain organic-silica hybrid materials that combine the functional properties of the biopolymer with the stability and porosity of silica.<sup>19, 28, 29</sup> Functionalized chitosan-silica sorbents are useful as stationary phase in chromatographic separation columns.<sup>19, 27, 28</sup> In this paper, chitosan-silica hybrid materials were synthesized and functionalized with diethylenetriamine pentaacetic acid (DTPA) and ethyleneglycol tetraacetic acid (EGTA). The selectivity for the uptake of scandium(III) from nitrate leachates was investigated in binary, equimolar solutions of scandium(III) and iron(III) with respect to the functional group immobilized on the polymer matrix. The effective separation of scandium from the bauxite residue leachate was investigated in a column chromatography set-up with EGTA-chitosan-silica as resin material and by eluting the loaded column with solutions with an increasing HNO<sub>3</sub> gradient (decreasing pH).

## Experimental

### Chemicals

Tetraethyl orthosilicate (TEOS,  $\geq 99.0\%$  pure) was purchased from Merck KGaA (Darmstadt, Germany). Chitosan ( $\geq 99.0\%$  pure) was purchased from Sigma-Aldrich (Diegem, Belgium). Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O ( $\geq 99.0\%$  pure) was purchased from J.T. Baker Chemicals B.V. (Deventer, The Netherlands). Sc(NO<sub>3</sub>)<sub>3</sub>·xH<sub>2</sub>O (99.99% pure) was kindly supplied by Stanford Materials Corporation (Irvine, California, USA). Hydrochloric acid (37%), ethanol (99.99%) and sodium sulfite anhydrous (analytical reagent grade) were purchased from Fischer Scientific U.K (Loughborough, UK). Ammonia (25 w%), *n*-

heptane (99+%), nitric acid (65+%), gallium standard (1000  $\mu\text{g}/\text{mL} \pm 0.4\%$ ), lanthanum standard (1000  $\mu\text{g}/\text{mL} \pm 0.3\%$ ), cerium standard (1000  $\mu\text{g}/\text{mL} \pm 2 \mu\text{g}$ ) and holmium standard (1000  $\mu\text{g}/\text{mL} \pm 0.4\%$ ) were purchased from Chem-Lab NV (Zedelgem, Belgium). Serva silicon solution was purchased from SERVA Electrophoresis GmbH (Heidelberg, Germany). Acetic acid (100%) and sodium hydroxide (min 97.0%) were purchased from VWR International (Heverlee, Belgium). Pyridine (99+%), methanol (99.99%), acetic acid anhydride (99+%), sulfuric acid (96%) and diethylenetriamine pentaacetic acid (DTPA, 98+%) were purchased from Acros Organics (Geel, Belgium). Ethyleneglycol tetraacetic acid (EGTA, ultrapure grade; 97.0%) was purchased from Amresco Inc (Solon, Ohio, USA). *N*-(3-dimethylaminopropyl)-*N'*-ethylcarbodiimide hydrochloride (EDC, 99%) was purchased from Fluorochem (Hadfield, UK). The bauxite residue, precursor of the red mud leachates which have been studied in this work, was provided by the Aluminum of Greece Company, which is located at Agios Nikolaos, Greece. All products were used as received, without further purifications.

### Equipment and analysis

FTIR spectra were recorded on a Bruker Vertex 70 spectrometer (Bruker Optics). Samples were examined as such using a Platinum ATR single reflection diamond attenuated total reflection (ATR) accessory. CHN (carbon, hydrogen, nitrogen) elemental analyses were obtained with the aid of a CE Instruments EA-1110 element analyser. Metal ion concentrations were determined by means of total-reflection X-ray fluorescence (TXRF) on a Bruker S2 Picofox TXRF spectrometer. To perform the sample preparation for a TXRF measurement, the unknown metal ion solution (900  $\mu\text{L}$ ) is mixed in an Eppendorf tube with a 1000  $\text{mg}\cdot\text{L}^{-1}$  gallium standard solution (100  $\mu\text{L}$ ) and stirred. A small amount of this prepared solution (5  $\mu\text{L}$ ) is put on a small quartz plate, pre-coated with a hydrophobic silicone solution (about 10  $\mu\text{L}$ ), and dried in an oven at 60 °C. Quantification of the metal ion concentration is derived from the absolute, known concentration of the gallium standard element and signal ratio of the metal of interest and the gallium standard. Centrifugation was done by means of a Heraeus Megafuge 1.0 centrifuge. The MPLC chromatography separation set-up was composed of a Büchi chromatography pump B-688, to control the pressure and the eluent flow, and a glass Büchi BOROSILIKAT 3.3 column tube, N° 17988 with dimensions 9.6 mm  $\times$  115 mm (bed volume = 8.3 mL). Separated compounds were collected with the aid of a Büchi Automatic Fraction Collector B-684. The distinct fractions were monitored by *ex-situ* analysis of the fractions with Inductively Coupled Plasma Mass Spectrometry (ICP-MS, Thermo Electron X Series).

### Methods

Chitosan-silica hybrid materials were made according to the *in-situ* Stöber based method as described previously.<sup>19</sup> In this work, also the consecutive functionalization with DTPA from its anhydride was described. The immobilization of EGTA

proceeded differently, according to the method described by Zhao *et al.*<sup>30</sup> In this procedure, EGTA and chitosan-silica were combined with 1-ethyl-3-(3-dimethylaminopropyl) carbodiimide (EDC) at 40 °C. EDC is a water soluble cross-linking agent that activates carboxyl groups for the coupling of primary amines.<sup>31</sup> The leaching of bauxite residue was carried out by constant agitation for 24 h at 160 rpm and 25 °C. The leaching experiments were carried out with a 0.20 N HNO<sub>3</sub> solution with a liquid-to-solid ratio of 50:1.<sup>14</sup> The elemental composition of the native bauxite residue leachate is presented in Table 1. Note the low concentration of scandium in comparison with the concentrations of the major elements. The leachates were filtrated to remove solid particles.

Adsorption experiments were conducted by adsorption in batch mode, in aliquots of a properly diluted stock solution. Stock solutions were kept at pH 1.00. To adjust the experimental pH, 1.0 M HCl or 0.1 M NaOH was added to decrease or increase the pH, respectively. Functionalized particles were then added to the vials. Solutions were stirred at room temperature with a magnetic stirring bar at 300 rpm for 4 h. Next, the particles were separated from the aqueous solution by filtration, making use of a regenerated cellulose syringe filter with a pore size of 0.45 μm. The remaining metal ion concentration of the aqueous solution was measured by TXRF. The amount of metal ions adsorbed onto the chitosan-silica particles was then determined using the following formula:

$$q_e = \frac{(c_i - c_e)V}{m_{ads}} \quad (1)$$


In this formula,  $q_e$  is the amount of adsorbed metal ions at equilibrium (mmol·g<sup>-1</sup> adsorbent),  $c_i$  is the initial metal ion concentration in aqueous solution (mmol·L<sup>-1</sup>),  $c_e$  is the equilibrium metal ion concentration in aqueous solution (mmol·L<sup>-1</sup>),  $V$  is the volume of the solution (0.010 L) and  $m_{ads}$  is the mass of the adsorbent (0.025 g).

Column experiments were performed with a leachate of Greek bauxite residue. The column (bed volume = 8.3 mL) was packed with EGTA-chitosan-silica and connected to a chromatography pump to control the pressure (max. 10 bar) and the eluent flow. The experiments were preceded by thorough washing of the column with demineralized water, followed by conditioning of the column with a solution of HNO<sub>3</sub>, set at pH 1.50 (same as leachate). After addition of the sample to the column (10 mL), a decreasing pH gradient was applied with diluted solutions of HNO<sub>3</sub> in order to elute the coordinated ions from the column. The distinct fractions (5 mL) were monitored by *ex-situ* analysis of the fractions with ICP-MS to determine the respective metal ion concentrations.

## Results and Discussion

### Synthesis

DTPA-chitosan-silica and EGTA-chitosan-silica were successfully synthesized. The hypothesis was that immobilization of these ligands on a matrix of chitosan-silica material would result in particles that show a high selectivity for scandium. Immobilization of the functional groups proceeded by an amide reaction with the free available amino groups on the chitosan moieties of the hybrid particles. The resulting structure is shown in Figure 1. Both sorbents appeared as white powders.

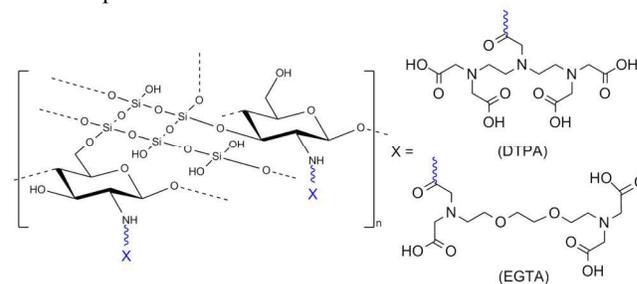

**Figure 1.** Chemical structure of chitosan-silica, functionalized with DTPA or EGTA.

A summary of the characterization results (obtained mass, FT-IR and CHN) is given in Table 2. From these results, the hybridization and functionalization of the chitosan-silica matrix was confirmed. In the chitosan-silica hybrid materials, the ratio organic:inorganic is approximately 1:4. By functionalization with organic ligands, the share of the organic component increases. From the respective values, it was concluded that the degree of functionalization was slightly higher for DTPA-chitosan-silica, compared to EGTA-chitosan-silica

### Kinetics

The kinetics of scandium adsorption were investigated with DTPA-chitosan-silica and EGTA-chitosan-silica in single-element nitrate solutions of scandium, with contact times ranging from 5 to 360 min (Figure 2). Equilibrium was reached after 120 min, characterized by the beginning of a plateau in the adsorption curve. The plateau value corresponded for DTPA-chitosan-silica to an adsorption amount of 0.20 mmol Sc(III) per gram of sorbent material. This appears to be a low value, but corresponds to 100% recovery of the scandium ions present in the aqueous solution. The initial aqueous feed contains 0.50 mM of scandium ions, which approaches the low concentration of scandium in diluted leachates of bauxite residue. For EGTA-chitosan-silica only 75% of the scandium present was adsorbed (0.15 mmol Sc(III) per gram of sorbent material). The lower adsorption amount for EGTA-chitosan-

**Table 1.** Initial elemental composition of the native leachate of Greek bauxite residue. ΣLn comprises all lanthanide elements (La, Ce, Pr, Nd, Sm, Eu, Gd, Tb, Dy, Ho, Er, Tm, Yb, and Lu)

Element	Na	Ca	Al	Fe	Si	Ti	Sc	ΣLn
Concentration (ppm)	1104	939	670	106	558	106	2	6


silica can be explained by the lower degree of functionalization, compared to DTPA-chitosan-silica (Table 2). Optimization of the synthesis procedure could improve this. In order to fully ensure equilibrium conditions before analyzing the residual concentration, all the following experiments were performed for an equilibration time of 240 min (4 h).

## ARTICLE

**Table 2.** Summary of characterization results for pure chitosan-silica, DTPA-functionalized chitosan-silica and EGTA-functionalized chitosan-silica

Material	Mass yield (g)	Characteristic peak wavelengths (cm <sup>-1</sup> )	Peak assignment	% C	% organic <sup>i</sup>
Chitosan-silica	10.2 ± 0.8	3366 (broad band)	O-H stretch + N-H stretch	8.09 ± 0.06	20.1
		1559	C-N stretch		
		1069	Si-O-Si symmetric stretch		
DTPA-chitosan-silica	9.5 ± 0.5	3366 (broad band)	O-H stretch + N-H stretch	11.85 ± 0.21	29.5
		1636	C=O stretch amide		
		1397	Symmetric vibration COO <sup>-</sup>		
		1065	Si-O-Si symmetric stretch		
EGTA-chitosan-silica	7.5 ± 0.5	3284 (broad band)	O-H stretch + N-H stretch	11.02 ± 0.06	27.4
		1636	C=O stretch amide		
		1376	Symmetric vibration COO <sup>-</sup>		
		1071	Si-O-Si symmetric stretch		


<sup>i</sup> From the % C in the chitosan starting product (40.19%), an estimate can be made for the share of the organic component in the hybrid particles.

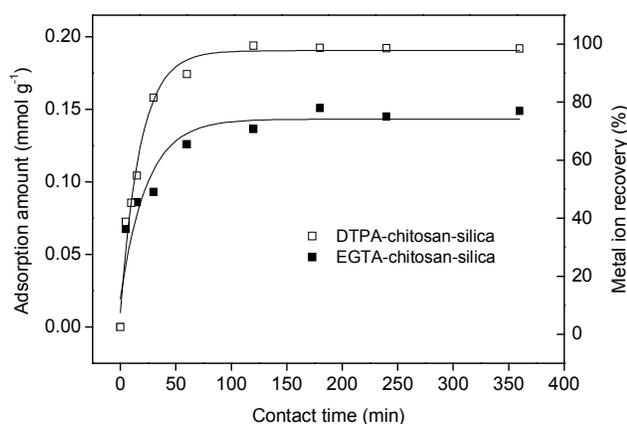

**Figure 2.** Kinetics experiment. Sc(III) adsorption with DTPA-chitosan-silica and EGTA-chitosan-silica. Experimental conditions:  $m_{\text{ads}} = 25.0$  mg,  $V = 10.0$  mL,  $c_{\text{in}} = 0.50$  mM,  $\text{pH}_{\text{eq}} = 2.02$ .

### Influence of pH

Adsorption was investigated as a function of the equilibrium pH. The pH is an important parameter for adsorption, as it determines protonation and deprotonation of the functional groups immobilized on the sorbent, and thus the mechanism of ion exchange and chelation. The influence of the equilibrium pH was investigated in single-element solutions of Sc(III) and Fe(III). In first instance, only DTPA-chitosan-silica was considered (Figure 3).

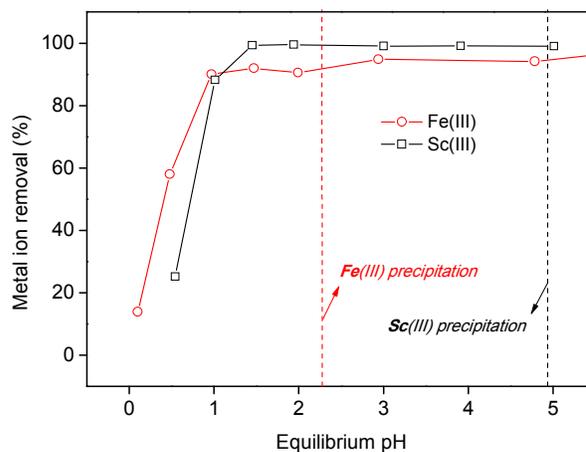

**Figure 3.** Influence of the equilibrium pH on the removal of Fe(III) and Sc(III) ions from single-element solutions in the presence of DTPA-chitosan-silica. The vertical dashed lines indicate the respective pH values at which precipitation of Fe(III) and Sc(III) occurs because of hydrolysis. Experimental conditions:  $m_{\text{ads}} = 25.0$  mg,  $V = 10.0$  mL,  $c_{\text{in}} = 0.50$  mM, contact time = 4 h.


When interpreting these data, one has to pay attention to the fact that both metal ions are prone to hydrolysis. As a consequence, insoluble  $\text{Fe}(\text{OH})_3$  and  $\text{Sc}(\text{OH})_3$  compounds are formed when increasing the pH. Since the adsorption amount is in principle calculated from the residual concentration of the aqueous phase at equilibrium, one could make the wrong assumption that all metal ions removed from solution are effectively adsorbed. From the respective solubility product

constants ( $K_{sp}(\text{Fe}(\text{OH})_3) = 2.79 \times 10^{-39}$ , and  $K_{sp}(\text{Sc}(\text{OH})_3) = 2.22 \times 10^{-31}$ )<sup>32</sup> and the metal ion concentration (0.50 mM), the pH at which precipitation occurs was calculated. This resulted in a value of 2.25 for Fe(III) and 4.88 for Sc(III). At higher pH values, one has to take into account precipitation as a phenomenon competing with adsorption in the removal of the corresponding metal ions from solution.

The main challenge for the isolation of pure scandium from leachates of bauxite residue is to obtain selectivity for scandium especially compared to iron. Both elements behave chemically very similarly and it is therefore difficult to mutually separate them from a matrix of lots of other elements, like calcium, silicon and titanium. Moreover, the concentration of iron in the leachates from bauxite residue is usually much higher than that of scandium. From Figure 3 it is evident that the affinity of DTPA-chitosan-silica is high for both Fe(III) and Sc(III). Both metal ions are (almost) fully adsorbed. We can assume that the metal ions are adsorbed because the plateau value is already reached at pH 1.50, which is below the pH range at which iron or scandium precipitates by hydrolysis reactions. It is further observed that the adsorption of Fe(III) starts at lower pH in comparison with Sc(III). This indicates a higher affinity for Fe(III), compared to Sc(III).

### Hydrolysis

One could think of pH variation as a way to separate Fe(III) and Sc(III) since hydrolysis occurs at lower pH values for Fe(III) in comparison with Sc(III).<sup>32</sup> Precipitation of Fe(III) and Sc(III) was therefore investigated as a function of the equilibrium pH in an equimolar ( $c_{aq} = 0.50$  mM), binary solution of Fe(III) and Sc(III) (Figure 4). Although significant precipitation (> 50 %) is observed for Fe(III) at lower pH values compared to Sc(III), we can also observe in Figure 4 that co-precipitation of scandium occurs.

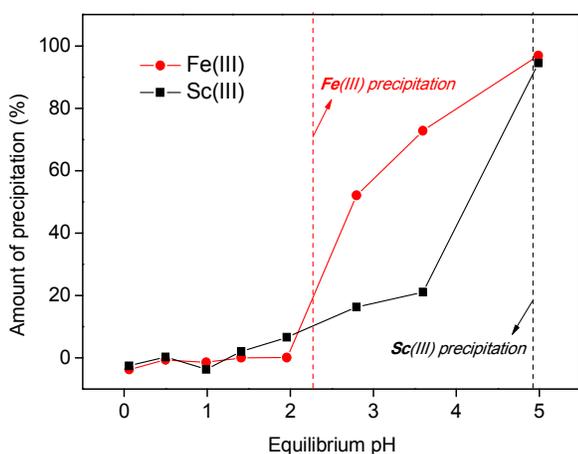

**Figure 4.** Investigation of  $\text{Fe}(\text{OH})_3$  and  $\text{Sc}(\text{OH})_3$  precipitation as a consequence of hydrolysis. The amount of precipitation is presented as a function of the equilibrium pH. The vertical dashed lines indicate the respective pH values at which precipitation of Fe(III) and Sc(III) occurs because of hydrolysis. Experimental conditions:  $V = 10.0$  mL,  $c_i = 0.50$  mM.

Although at pH 3.50 almost four times more Fe(III) is precipitated compared to the amount of Sc(III), the 20% loss of

scandium is not acceptable, taking into account its high economical value. Moreover, in real leachates of bauxite residue, the relative amount of iron is significantly larger than that of scandium. It is therefore expected that also the amount of scandium co-precipitation would be significantly higher in real samples (if not 100%). This method was therefore not considered appropriate in the search for a method to isolate scandium efficiently from leachates of bauxite residue. Also the possibilities of adding reducing agents (like zinc powder or sodium sulphite), or varying the counter anion (like sulphate or chloride) were investigated, but none of these methods were found to be useful. These observations only convinced us more of the hypothesis that an *intrinsically selective* adsorbent must provide the solution.

### Selectivity experiment

Variation of the functional group immobilized on the chitosan-silica particles appeared to be a more successful strategy to obtain scandium selectivity. Since DTPA had already been proven to be a very efficient chelating molecule for rare earths, the functionalization of the chitosan-silica resin with DTPA groups was tested first as regards its selectivity for scandium.<sup>18</sup> However, as was concluded from Figure 3, the affinity of DTPA-functionalized particles was higher for Fe(III) compared to Sc(III). This is a consequence of the corresponding stability constants between DTPA and Fe(III) or Sc(III), respectively (Table 3).

**Table 3.** Stability constants (log K values) for complexes formed between often used poly (amino) carboxylic ligands and the metal ions Fe(III), Sc(III), Nd(III) (as a representative element for the lanthanides).<sup>33</sup>

Organic ligand	Fe(III)	Sc(III)	Nd(III)
IDA <sup>i</sup>	11.1	9.9	6.5
NTA <sup>ii</sup>	15.9	12.7	11.3
EDTA <sup>iii</sup>	25.1	23.1	16.6
DTPA	27.3	26.3	21.6
EGTA	20.5	25.4	16.3


<sup>i</sup>IDA = iminodiacetic acid

<sup>ii</sup>NTA = nitrilotriacetic acid

<sup>iii</sup>EDTA = ethylenediamine tetraacetic acid

By closer inspection of different organic ligands and their corresponding stability constants with Sc(III) and Fe(III), one can see that EGTA has a remarkably higher affinity for Sc(III) compared to Fe(III), a difference of factor  $10^5$  (Table 3). The opposite is true for DTPA. Although DTPA has a high stability constant with Sc(III) (log K = 26.3), the stability constant with Fe(III) is even higher (log K = 27.3). To confirm the hypothesis that EGTA-chitosan-silica is more suited to separate Sc(III) from Fe(III) (and the other elements present in the leachate), the selectivity of both ligands was investigated in a binary solution of Fe(III) and Sc(III) ( $c_{aq} = 0.50$  mM for each metal ion). In Figure 5, the metal ion removal is presented as a

function of the equilibrium pH for both DTPA-chitosan-silica (a) and EGTA-chitosan-silica (b), to be able to compare the adsorption behaviour of both sorbents. It becomes clear that the selectivity is reversed by switching from DTPA to EGTA as chelating ligand. With EGTA-chitosan-silica, we are able to reach maximal adsorption for Sc(III) at pH 1.25, at which yet no Fe(III) is adsorbed at all. This high difference in selectivity is quite remarkable for two such chemically similar elements and could not be obtained with DTPA-chitosan-silica. Not only did DTPA-chitosan-silica show a higher affinity for Fe(III) compared to Sc(III), also the affinity profiles were much more similar. This is a consequence of the small difference (factor 10) between the corresponding stability constants (Table 3).<sup>33</sup>

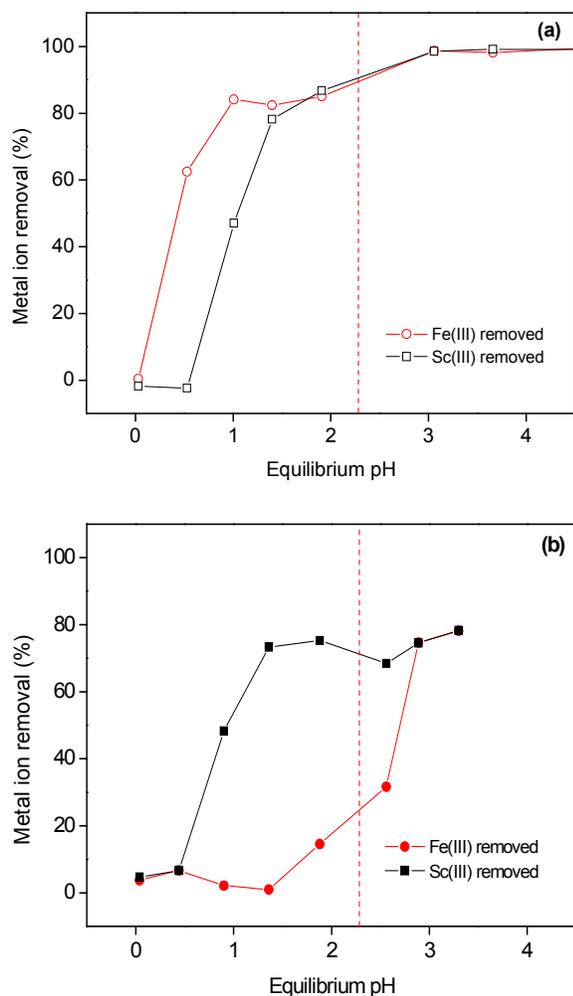


**Figure 5.** Metal ion removal from a binary, equimolar solution of Fe(III) and Sc(III) in the presence of DTPA-chitosan-silica (a) or EGTA-chitosan-silica (b). The vertical dashed line indicates the pH at which precipitation of Fe(III) occurs because of hydrolysis. Experimental conditions:  $m_{\text{ads}} = 25.0$  mg;  $V = 10$  mL;  $c_i = 0.50$  mM; adsorption time = 4 h.

At pH 1.50 (Figure 5b), no Fe(III) is adsorbed by EGTA-chitosan-silica, yet 80% of the Sc(III) ions are adsorbed from the aqueous solution. This remarkably higher affinity for scandium can be exploited in a column chromatography set-up

to separate scandium from the other components present in a leachate of bauxite residue.

### Reusability


After adsorption of metal ions from solution, stripping of the immobilized ions is required for further processing and regeneration of the sorbent. No concentrated acid or solutions of strongly chelating agents were necessary to desorb strongly immobilized Sc(III) ions from EGTA-chitosan-silica. By simply contacting the loaded particles with a HNO<sub>3</sub> solution, 100% stripping was observed for HNO<sub>3</sub> concentrations higher than 0.75 M. The reusability was investigated for EGTA-chitosan-silica by repeating the adsorption/desorption cycle seven times. The resulting adsorption values were each time compared with the adsorption amount in the first cycle to determine the adsorption efficiency (Figure 6). The adsorption efficiency decreased with about 10% in the second adsorption cycle. This is probably due to partial hydrolysis of the immobilized EGTA groups by the acid used in the first stripping step. The residual capacity remained quite constant. After the 7<sup>th</sup> adsorption cycle, the adsorption efficiency was still 90%. The (minimal) decreases observed after the second cycle could more likely be attributed to physical losses because of the manual handlings during consecutive adsorption/desorption cycles, rather than to physical or chemical damage to the particles because of the stripping treatment, as it is expected that all loosely bound EGTA-ligands have been hydrolyzed during the first stripping step.

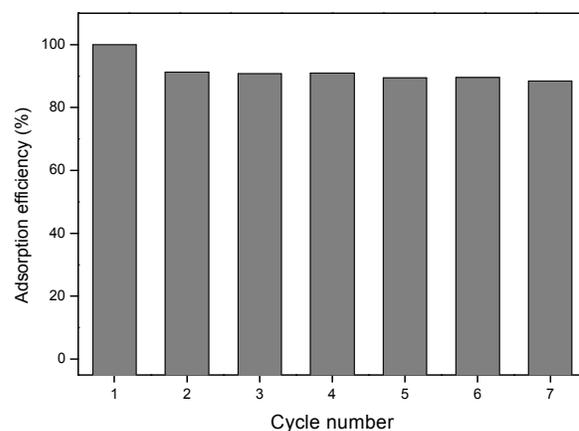

**Figure 6.** Reusability of EGTA-chitosan-silica. Adsorption from an aqueous solution of Sc(NO<sub>3</sub>)<sub>3</sub>. Stripping with 1.0 M HNO<sub>3</sub> (10 mL). Experimental conditions:  $m_{\text{ads}} = 25.0$  mg;  $V = 10$  mL;  $c_i = 0.50$  mM; adsorption time = 4 h; stripping time = 1 h.

### Column separation experiments

The higher the affinity of a given metal ion for a functionalized resin, the slower the migration through the chromatography column will be. The isolation of scandium was investigated by the principle of ion-exchange column chromatography with EGTA-chitosan-silica as resin material in an MPLC-set-up. A bauxite residue leachate sample was added on top of the column, pre-equilibrated at a pH of 1.50, just like the leachate.

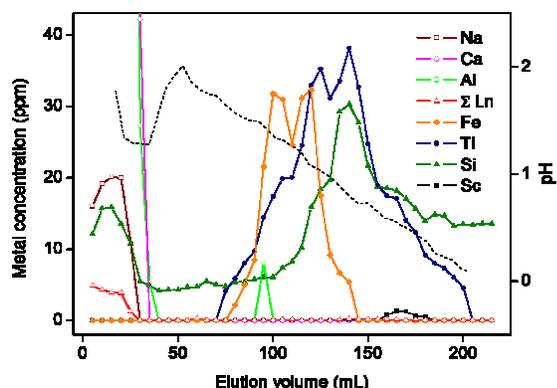


**Figure 7.** Chromatogram of scandium separation from a bauxite residue leachate by ion-exchange column chromatography with EGTA-chitosan-silica as resin material and a decreasing pH gradient. The metal concentration is presented as a function of the elution volume.  $\Sigma$ Ln comprises all lanthanide elements (La, Ce, Pr, Nd, Sm, Eu, Gd, Tb, Dy, Ho, Er, Tm, Yb, and Lu). The dotted line represents the pH of the distinct fractions (right axis).

The amount of scandium in the leachate (1 ppm) is at least 150 times lower than that of each of the major elements, like iron (233 ppm) (Table 1). Elution with aqueous solutions of  $\text{HNO}_3$  (at a flow rate of 40 mL/h) then enabled the collection of distinct fractions of metal ions in the order of affinity for the resin material. A decreasing pH gradient was applied (from pH 2.00 to pH 0.00) in order to induce consecutive desorption of the distinct complexed metal ions. The resulting chromatogram (metal ion concentration as a function of elution volume) is presented in Figure 7.

Peaks dropping after the first few fractions are explained by the fact that the pH gradient started from pH 2.00, while the column was set before at a lower pH of 1.50. Given the high affinity for Sc(III), it is observed that the peak of Sc(III) is located after 150 mL, corresponding to an elution pH of 0.50, at

which most of the other elements have eluted already. Moreover, the big difference between scandium and the lanthanides is remarkable. However, the lower affinity of the resin for the lanthanides can be explained by the lower stability constant between EGTA and the lanthanides compared to scandium. Further it has to be noted that the desorbed scandium fractions still contain titanium and silicon impurities. Nevertheless, the largest fractions of these ions have eluted earlier. The highest breakthrough peaks of Ti(IV) and Si(IV) are situated around a pH value of 0.80 already. These observations indicate that an even better separation could be obtained by optimization of the experimental conditions. Possibilities to improve the separation include a slower decreasing pH gradient, a lower flow rate, a longer column and the consideration of other types of eluents.

A second column experiment was performed by just changing the pH gradient and the flow rate (to 30 mL/h). The same column (with equal amounts of the same material) was used as in the first experiment. Elution was immediately started from pH 1.50 and more fractions were collected before eluting with pH 0.50 to strip off scandium from the column. The resulting chromatogram is presented in Figure 8. In this figure, unlike Figure 7, the breakthrough of the different metal ions is presented in a different way for the sake of clarity. To be able to compare the behaviour of scandium to the major elements (the latter presented in significantly higher concentrations in the leachate) the breakthrough is better presented as a percentage of the initial concentration, in a cumulative way (adding up from 0 to 100%) as a function of elution volume. A sudden pH increase is observed during column loading. This can probably be attributed to an increase of the ionic strength of the column.<sup>34</sup> Next to that, the effect of the experimental optimization becomes very clear from Figure 8. By going faster to lower pH values, all elements, except for scandium, start to

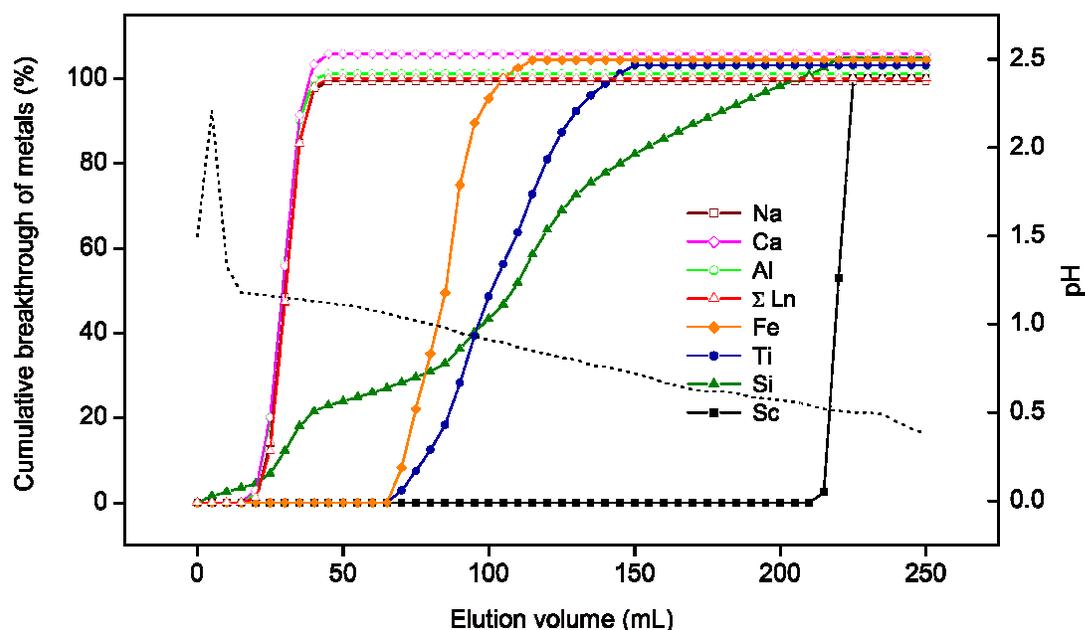

**Figure 8.** Optimized separation of scandium from a bauxite residue leachate by ion-exchange column chromatography with EGTA-chitosan-silica as resin material and a decreasing pH gradient. The cumulative breakthrough of the distinct metals is presented as a function of the elution volume.  $\Sigma$ Ln comprises all lanthanide elements (La, Ce, Pr, Nd, Sm, Eu, Gd, Tb, Dy, Ho, Er, Tm, Yb, and Lu). The dotted line represents the pH of the distinct fractions (right axis).

elute at lower elution volumes. Moreover, elution at pH values between 1.00 and 0.50 was maintained for a longer time. This allowed all the iron, titanium and silicon to fully elute from the column before scandium was stripped from the column at pH 0.50, in only two fractions. EGTA-chitosan-silica has such a high affinity for scandium, so that we managed to separate it from a real leachate of bauxite residue in only one simple chromatography cycle, with a high recovery rate (about 25 bed volumes). To the best of our knowledge, a higher selectivity for scandium has not been reported before. Both scandium fractions could then be combined and concentrated by evaporation for further processing.

## Conclusions

Functionalization of chitosan-silica particles with EGTA groups resulted in a hybrid material with an exceptionally high adsorption affinity for scandium, higher than that of a similar hybrid material, functionalized with DTPA groups. The high selectivity for scandium was confirmed in equimolar, binary solutions of Sc(III) and Fe(III) and eventually exploited to separate scandium from the other components (mainly iron, titanium and silicon) in a HNO<sub>3</sub> leachate of Greek bauxite residue. Scandium was isolated from the other elements by ion-exchange column chromatography, by applying a decreasing pH gradient with aqueous solutions of HNO<sub>3</sub>. Scandium broke through the column at a pH of 0.50, a much lower value than the ones observed for the other metal ions present in the leachate. This allowed to strip pure scandium fractions from the column with a high recovery rate.

## Acknowledgements

This work was funded by VITO, the Research Foundation - Flanders (FWO, PhD fellowship to JR) and KU Leuven (DBOF grant to CRB and IOF-KP RARE<sup>3</sup>). The authors also wish to thank Aluminum of Greece for providing the bauxite residue sample. Michèle Vanroelen is thanked for performing the ICP measurements.

## Notes and references

<sup>a</sup> KU Leuven, Department of Chemistry, 3001 Heverlee, Belgium

<sup>b</sup> KU Leuven, Department of Chemical Engineering, 3001 Heverlee, Belgium

<sup>c</sup> VITO, Sustainable Materials Management, 2400 Mol, Belgium

\* Corresponding author: [Koen.Binnemans@chem.kuleuven.be](mailto:Koen.Binnemans@chem.kuleuven.be), Tel. +32 16 32 74 46.


† Electronic Supplementary Information (ESI) available: detailed synthesis procedures and IR-spectra. See DOI: 10.1039/b000000x/

- K. Binnemans, P. T. Jones, B. Blanpain, T. Van Gerven and Y. Pontikes, *J. Clean. Prod.*, 2015, **99**, 17-38.
- Y. V. Nancharaiyah, S. Venkata Mohan and P. N. L. Lens, *Bioresour. Technol.*, 2015, **195**, 102-114.
- H. Dong, J. Zhao, J. Chen, Y. Wu and B. Li, *Int. J. Miner. Process.*
- Z. Shengqiang, H. Xiuyang and W. Dahui, *Rare Metal Mat. Eng.*, 2015, **44**, 73-78.
- R. Banda, T. H. Nguyen, S. H. Sohn and M. S. Lee, *Hydrometallurgy*, 2013, **133**, 161-167.
- S. Massari and M. Ruberti, *Resour. Policy*, 2013, **38**, 36-43.
- K. Binnemans, P. T. Jones, B. Blanpain, T. Van Gerven, Y. Yang, A. Walton and M. Buchert, *J. Clean. Prod.*, 2013, **51**, 1-22.
- A. R. Hind, S. K. Bhargava and S. C. Grocott, *Colloid. Surface. A*, 1999, **146**, 359-374.
- G. Power, M. Gräfe and C. Klauber, *Hydrometallurgy*, 2011, **108**, 33-45.
- C. Klauber, M. Gräfe and G. Power, *Hydrometallurgy*, 2011, **108**, 11-32.
- M. Gräfe, G. Power and C. Klauber, *Hydrometallurgy*, 2011, **108**, 60-79.
- Z. Ahmad, *JOM*, 2003, **35**, 35-39.
- S. P. S. Badwal, F. T. Ciacchi and D. Milosevic, *Solid State Ionics*, 2000, **136-137**, 91-99.
- C. R. Borra, Y. Pontikes, K. Binnemans and T. Van Gerven, *Miner. Eng.*, 2015, **76**, 20-27.
- O. Petrakova, G. Klimentenok, A. Panov and S. Gorbachev, presented in part at the ERES2014: 1st European Rare Earth Resources Conference, Milos, 04-07/09/2014, 2014.
- W. Wang, Y. Pranolo and C. Y. Cheng, *Hydrometallurgy*, 2011, **108**, 100-108.
- M. T. Ochsenkühn-Petropoulou, K. S. Hatzilyberis, L. N. Mendrinou and C. E. Salmas, *Ind. Eng. Chem. Res.*, 2002, **41**, 5794-5801.
- J. Roosen and K. Binnemans, *J. Mater. Chem. A*, 2014, **2**, 1530-1540.
- J. Roosen, J. Spooen and K. Binnemans, *J. Mater. Chem. A*, 2014, **2**, 19415-19426.
- E. Guibal, *Sep. Purif. Technol.*, 2004, **38**, 43-74.
- N. Mati-Baouche, P.-H. Elchinger, H. de Baynast, G. Pierre, C. Delattre and P. Michaud, *Eur. Polym. J.*, 2014, **60**, 198-212.
- A. J. Varma, S. V. Deshpande and J. F. Kennedy, *Carbohydr. Polym.*, 2004, **55**, 77-93.
- S. E. Bailey, T. J. Olin, R. M. Bricka and D. D. Adrian, *Water Res.*, 1999, **33**, 2469-2479.
- E. Guibal, C. Milot and J. M. Tobin, *Ind. Eng. Chem. Res.*, 1998, **37**, 1454-1463.
- A. El Kadib, *ChemSusChem*, 2015, **8**, 217-244.
- K. Inoue, K. Yoshizuka and K. Ohto, *Anal. Chim. Acta*, 1999, **388**, 209-218.
- S. S. Rashidova, D. S. Shakarova, O. N. Ruzimuradov, D. T. Satubaldieva, S. V. Zalyalieva, O. A. Shpigun, V. P. Varlamov and B. D. Kabulov, *J. Chromatogr. B*, 2004, **800**, 49-53.
- H. Zhao, J. Xu, W. Lan, T. Wang and G. Luo, *Chem. Eng. J.*, 2013, **229**, 82-89.
- E. Repo, J. K. Warchol, A. Bhatnagar and M. E. T. Sillanpää, *J. Colloid Interface Sci.*, 2011, **358**, 261-267.
- F. Zhao, E. Repo, D. Yin and M. E. Sillanpää, *J. Colloid Interface Sci.*, 2013, **409**, 174-182.
- S. K. Vashist, *Diagnostics*, 2012, **2**, 23-33.
- CRC Handbook of Chemistry and Physics*, CRC Press LLC, Boca Raton, USA, 2003-2004.
- D. D. Perrin, *Stability Constants, Part B Organic Ligands*, Pergamon, Oxford, 1979.
- C. D. Kennedy, *Biochem. Educ.*, 1990, **18**, 35-40.

## Table of content

## FULL PAPER

The recovery of pure scandium from leachates of Greek bauxite residue was investigated by ion-exchange adsorption. From batch experiments, it appeared that EGTA-chitosan-silica shows an exceptionally high selectivity for scandium. It was therefore used as resin material in a column-chromatography set-up to isolate pure scandium.

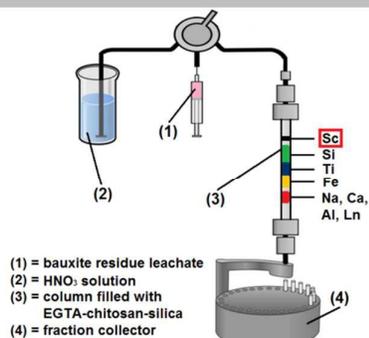

Joris ROOSEN, Stijn VAN ROSENDAEL, Chenna Rao BORRA, Tom VAN GERVEN, Steven MULLENS, and Koen BINNEMANS\*

[Page No. – Page No.]

**Recovery of scandium from leachates of Greek bauxite residue by adsorption on functionalized chitosan-silica hybrid materials**