

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

**Adsorption of Cr(VI) onto magnetic CoFe₂O₄/MgAl-LDH
composite and mechanism study**

Lin Deng, Zhou Shi^{*}, Xiaoxu Peng

Key Laboratory of Building Safety and Energy Efficiency, Ministry of Education, Department of Water Engineering and Science, College of Civil Engineering, Hunan University, Changsha 410082, PR China

*Corresponding author: Zhou Shi

Address: College of Civil Engineering, Yuelu Mountain, Hunan University, Changsha Hunan, 410082, China

E-mail address: 369329062@qq.com

Abstract

Magnetic materials as adsorbent can provide effective remove and quickly separate of pollutant in wastewater treatment. A magnetic $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ composite was successfully synthesized through low saturation coprecipitation method. The adsorption behaviors of Cr(VI) from aqueous solution by $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ were investigated. The adsorbents were characterized using scanning electron microscope (SEM), N_2 adsorption/desorption isotherms, X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FTIR) and X-ray photoelectron spectroscopy (XPS). Kinetic and equilibrium studies indicated that the experimental data of Cr(VI) adsorption were best described by pseudo-second-order kinetic and Langmuir models. The maximum adsorption capacity of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ for Cr(VI) was found to be 72.4 mg/g at an equilibrium time of 300 min and temperature of 283 K. Evaluation of the thermodynamics parameters ($\Delta H < 0$, $\Delta S < 0$ and $\Delta G < 0$) revealed the adsorption process was exothermic and spontaneous. The mechanisms study showed that the adsorption of Cr(VI) onto $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ likely involved adsorption/surface complexation and ion exchange interaction. This study demonstrated that the magnetic $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ composite was an effective adsorbent for Cr(VI) removal with quick separation.

1. Introduction

Effluents containing hexavalent chromium Cr(VI) generated from electroplating, textile, metal finishing, mining, leather tanning and pigment manufacturing have become a major concern due to its high toxicity, carcinogenic and mutagenic properties to both the environment and living organisms.¹⁻⁴ To prevent the harmful impact of Cr(VI) on public health, many countries around the world have regulations of the maximum permissible concentration of Cr(VI) in natural or drinking water. A maximum allowable limit of 0.05 mg/L for total chromium has been set by the World Health Organization (WHO) drinking water guidelines,⁵ and the permissible Cr(VI) concentration in drinking water is 0.05 mg/L in China.⁶ Therefore, to protect the environment and human health, it has become imperative to find an effective way to remove Cr(VI) from wastewaters to an acceptable threshold before releasing them into water bodies.

Various physicochemical and biological techniques have been developed to eliminate Cr(VI) from industrial wastewaters including chemical precipitation,⁷ ion exchange,⁸ membrane filtration,⁹ solvent extraction,¹⁰ adsorption^{2-4,11} and biological processes,¹² etc. Among these techniques, adsorption method has attract much attention due to its significant advantages such as simplicity of design and operation, cost-effective, high efficiency, recycle of adsorbent, and no secondary pollution.¹³ The key to practical application of adsorption requires the adsorbent with high surface area for more binding sites and strong adsorption affinity to adsorbate. Thus, many types of adsorbents such as low-cost or easily available clays, carbon materials, nanomaterials, biomaterials, by-products and waste materials have been investigated extensively and systematically for the removal of Cr(VI) from aqueous solution.¹⁴⁻¹⁷

Layered double hydroxides (LDHs) is an anionic clay, whose chemical composition can be generally expressed as $[M^{2+}_{1-x}M^{3+}_x(OH)_2]^{x+}[A^{n-}_{x/n}]^{x-} \cdot mH_2O$, where M^{2+} and M^{3+} represent divalent metal cations (Mg^{2+} , Ni^{2+} , Zn^{2+} , Ca^{2+} , Co^{2+} , Cu^{2+} or Cd^{2+}) and trivalent metal cations (Al^{3+} , Fe^{3+} , Cr^{3+} or V^{3+}), respectively, A^{n-} represent the interlayer anions (CO_3^{2-} , NO_3^- or Cl^-) that balance the positive charge on the layers, and x is donated as the molar ratio of $M^{2+}/(M^{2+} + M^{3+})$.^{18,19} In recent years, LDHs such as LiAl-LDH,²⁰ MgAl-LDH,²¹ Fe²⁺-doped

MgAl-LDH,²² and ZnAl-LDH,²³ have been detailed investigated for the removal of Cr(VI) ions from aqueous solution, and the LDHs have exhibited great adsorption capacity for Cr(VI) because of its high surface area, layered structure, and interlayer anion mobility of its A^n -host.²⁴ However, LDHs suffer from separation convenience, preventing them from industrial application scopes greatly.^{25,26} To overcome this issue, it is necessary to explore novel LDHs-based adsorbents, which possess higher adsorption capacity and separation property.

Magnetic materials have been introduced into the adsorbent recently, and the magnetic separation method has been considered as high separation efficiency, low cost and convenient technique in comparison with the traditional separation methods such as precipitation, centrifugation or filtration. Porous materials can provide effective sites for adsorption process; moreover, their irregular and wide pore size distribution will be beneficial for the adsorption. Stimulated by the promising application of the hybrid systems with porous materials and magnetic particles with characteristics of high efficiency, fast adsorption rate and facile separation, a few reports have been made in preparing of different types of magnetic porous adsorbents.^{27,28} Iron oxide (Fe_3O_4) is the most commonly used magnetic material recently due to its low cost and low toxicity. Mohammadi et al.²⁹ synthesized superparamagnetic sodium alginate-coated Fe_3O_4 nanocomposites (Alg- Fe_3O_4) by in situ coprecipitation method, and the adsorbent exhibited a maximum adsorption capacity of 47.84 mg/g for adsorption of malachite green dye onto Alg- Fe_3O_4 . Fang et al.³⁰ prepared an ethylenediamine (EDA) functionalized Fe_3O_4 (EDA- Fe_3O_4) for removing Cr(VI) from aqueous solution, and the maximum adsorption capacity was found to be 81.5 mg/g at pH 2.0. Li et al.³¹ reported the recyclable CNTs/ Fe_3O_4 magnetic composites synthesized through a facile hydrothermal method, and the adsorbent showed magnetic separability and strong adsorption behaviors in the treatment of bisphenol A (BPA) in aqueous solution. However, Fe_3O_4 is susceptible to acid conditions, which might decrease the magnetic separability of adsorbents; moreover some reactants (such as ethylenediamine) for preparation of Fe_3O_4 may be harm to the environment.³²

Spinel ferrites (e.g. $MnFe_2O_4$, $CoFe_2O_4$, $NiFe_2O_4$, $CuFe_2O_4$ and $MgFe_2O_4$) have been widely used in electrical and practical applications of information storage system, magnetocaloric refrigeration, and ferrofluid technology; and they have also been employed

for water purification for the last several years, but their adsorption efficiency was not satisfactory.^{33,34} In this study, CoFe_2O_4 was selected as the magnetic core. To the best of our knowledge, the $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ composite composed of CoFe_2O_4 as the magnetic core coated with the nanostructured crystalline MgAl-LDH , especially in the field of application of the adsorbent for removing Cr(VI) from aqueous solution, has rarely been reported before.

The objective of this study was to evaluate the potential of using $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ to remove Cr(VI) from aqueous solution. The adsorption properties as functions of varied operational conditions (solution pH, contact time, initial Cr(VI) concentration, temperature and coexisting ions) were investigated systematically. Adsorption kinetics, isotherms and thermodynamics were studied to expound the specific adsorption mechanism of Cr(VI) onto $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$. The physical structure and chemical properties of the as-prepared $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ were characterized in detail by scanning electron microscope (SEM), N_2 adsorption/desorption isotherms, X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FTIR) and X-ray photoelectron spectroscopy (XPS).

2. Materials and methods

2.1 Materials

The chemicals, $\text{CoCl}_2 \cdot 4\text{H}_2\text{O}$, $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$, $\text{Al(NO}_3)_3 \cdot 9\text{H}_2\text{O}$, $\text{Mg(NO}_3)_2 \cdot 6\text{H}_2\text{O}$, Na_2CO_3 , NaOH , HCl , ammonia, ethylene glycol and ethyl alcohol were purchased from Tianjin Kemiou Chemical Reagent Co., Ltd., China. $\text{K}_2\text{Cr}_2\text{O}_7$ were supplied from Tianjin Hengxing Chemical Reagent Co., Ltd., China. All of the reagents were of analytical grade and were used as received without any further purification. Doubly distilled deionized water was used throughout this study. Various Cr(VI) solutions with different concentrations were prepared by dissolving $\text{K}_2\text{Cr}_2\text{O}_7$ in deionized water.

2.2 Preparation of magnetic $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ composite

The CoFe_2O_4 nanoparticles were synthesized by hydrothermal synthesis method. 1.112 g of $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ and 0.4758 g $\text{CoCl}_2 \cdot \text{H}_2\text{O}$ were dissolved in a mixture of 60 mL of ethylene glycol solvent and 40 mL deionized water, followed by the addition of 4 mL of ammonia solution ($\text{NH}_3\text{H}_2\text{O}$). The above mixture was stirred vigorously for 1 h and then poured into a 100 mL Teflon-lined autoclave. The autoclave was heated to and maintained at 180°C for 24

h. After cooling to room temperature, the precipitate was washed several times with deionized water and ethanol, and dried at 60 °C for 12 h. The ethylene glycol serves as not only a high boiling point (197.3 °C) solvent to keep the volume of the reaction solution constant during the hydrothermal synthetic process being carried at relatively high temperature, but also a phase to prevent the newly formed reaction product, CoFe₂O₄ nanoparticles, from conglomerating. Ammonia solution (NH₃H₂O) has two functions: First, NH₃H₂O is an oxidizing agent to oxidize Fe²⁺ to Fe³⁺. Second, NH₃H₂O as a weak base can help Co²⁺ and Fe³⁺ to precipitate as hydroxides and then to form CoFe₂O₄ nanoparticles through dehydration in the hydrothermal synthetic process.

The magnetic CoFe₂O₄/MgAl-LDH composite was synthesized through low saturation coprecipitation method. A certain amount of prepared CoFe₂O₄ (0.5 g) was ultrasonically dispersed into 150 mL deionized water in 500 mL beaker for 20 min to obtain a uniform suspension, and then the beaker was transferred into a water bath at 60 °C with vigorous stirring. Meanwhile, a salt solution (100 mL) containing 0.125 mol/L Al(NO₃)₃·9H₂O and 0.25 mol/L Mg(NO₃)₂·6H₂O was dropwise added into the suspension, and an alkaline solution (100 mL) containing 3.375 g NaOH and 2.645 g Na₂CO₃ was added simultaneously to keep the pH at 10.0-10.5. After complete addition of the two solutions, the suspension was aged for 8 h, followed by washing with deionized water until the effluent solution is neutral. The resulting product was dried at 60 °C for 12 h.

2.3 Characterization methods

The morphologies of adsorbents were determined by Hitachi S-4800 SEM operating at 5 kV. The specific surface area and pore diameter measurements were carried out by nitrogen adsorption at 77 K using an automated gas sorption analyzer (Quantachrome Instruments, QuadraSorb Station 1). XRD data were collected on a Rigaku D/Max-2500 powder diffractometer with Cu K α radiation with a scan step of 0.02°. Infrared spectra of the adsorbents were recorded using a FT-IR spectrometer (Thermo Nicolet, Nexus-470, USA) at 400-4000 cm⁻¹. XPS measurements were performed on ESCALab220i-XL electron spectrometer from VG Scientific using 300W Al K α radiations.

2.4 Adsorption experiments

The adsorption of Cr(VI) from aqueous solutions onto the CoFe₂O₄/MgAl-LDH was

studied in a batch system. In each adsorption experiment, 50 mL of Cr(VI) solution with known concentration was put into a 120 mL polyethylene bottles. The solution pH measured by a pH meter (Orion Research, Inc, Model 868, USA) was adjusted to a predetermined value with 0.1 mol/L HCl or 0.1 mol/L NaOH, and 0.15 g CoFe₂O₄/MgAl-LDH was added into the above solution. Subsequently, the resulting mixture was stirred in a thermostatic water bath shaker to reach equilibrium except kinetic experiments. At the end of each experiment, the supernatant was filtered using 25-mm 0.45μm membrane filter, and the filtrate was then analyzed for the residual Cr(VI) concentration in solution. The residual Cr(VI) concentration in solution was determined with 1,5-diphenylcarbohydrazide spectrophotometric method using an ultraviolet spectrophotometer (Hitachi, U-3900, Japan). Blank experiments were run in parallel on Cr(VI) solutions, without addition of adsorbent, for the sake of comparison. All tests were carried out in triplicate, and their mean values were used in analyzing the data.

The removal efficiency (R , %) and the amount of Cr(VI) adsorbed at time t (q_t , mg/g) were calculated according to the formula:

$$R = \frac{C_0 - C_t}{C_0} \times 100\% \quad (1)$$

$$q_t = \frac{(C_0 - C_t) \times V}{m} \quad (2)$$

where C_0 (mg/L) and C_t (mg/L) are the liquid phase concentration of Cr(VI) at initial and time t (min), respectively. V (L) is the volume of Cr(VI) solution, m (g) is the mass of the adsorbent.

3. Results and discussion

3.1 Characterization of CoFe₂O₄/MgAl-LDH composite

Nitrogen adsorption-desorption isotherms were recorded to examine the surface and pore structure of MgAl-LDH, CoFe₂O₄, CoFe₂O₄/MgAl-LDH before and after Cr(VI) adsorption. Fig. S1 depicted the results of nitrogen adsorption-desorption isotherms. All of the four isotherm curves exhibited the representative type-IV curves with hysteresis loops, indicating the uniform mesoporous structure of the four samples. Table 1 showed the specific surface area, pore volume, and average pore diameter of the adsorbents.

Obviously, compared with the CoFe_2O_4 , the introduction of MgAl-LDH led to a distinct increase in BET surface area (from 15.12 to 120.75 m^2/g), pore volume (from 0.074 to 0.756 cc/g) and pore diameter (from 3.83 to 18.65 nm) of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$, which were beneficial to the adsorption of Cr(VI). The decrease in BET surface area, pore volume and pore diameter of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ after Cr(VI) adsorption indicated that Cr(VI) ions were probably adsorbed by the adsorbent into its pores and developed a layer of Cr(VI) substance on the surface. This was also in accordance with SEM results shown in Fig. S2, in which the adsorbent after Cr(VI) adsorption became more abnormal and a great deal of crystal adhered to the adsorbent surface.

XRD of MgAl-LDH, CoFe_2O_4 , $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ before and after Cr(VI) adsorption was carried out to identify the phase structure of adsorbents. It was observed in Fig. 1a that MgAl-LDH exhibited diffraction peaks at $2\theta=11.72^\circ$, 23.58° , 34.99° , 39.56° , 47.10° , 60.90° and 62.21° , which could be assigned to the (003), (006), (009), (015), (018), (110) and (113) planes of Mg/Al-LAH nanoplates (JCPDS: 89-0460).³⁵ The diffraction peaks of (009), (015), (018), (110) and (113) had relatively low intensities, while peaks of (003) and (006) were especially strong, indicating that the crystal grew along a certain axis. Fig. 1b showed the XRD patterns of CoFe_2O_4 . The diffraction signals located at (220), (311), (400), (422), (511) and (440) were ascribed to the characteristic peaks of single phase cubic spinel structure of CoFe_2O_4 (JCPDS: 22-1086).³⁴ The intensities of the characteristic reflections for both MgAl-LDH and CoFe_2O_4 phases in $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ composite were not obviously changed compared to those in pure MgAl-LDH and CoFe_2O_4 . Moreover, there were no other characteristic peaks detected in the XRD patterns of the adsorbent as shown in Fig. 1c, demonstrating that the synthesized adsorbent was a composite of MgAl-LDH and CoFe_2O_4 and the combination was probably a physical process. After adsorption of Cr(VI) from aqueous solution, the layered structure of the adsorbent was reconstructed (Fig. 1d). However, its XRD patterns were in good agreement with the characteristic peaks of CoFe_2O_4 , indicating that the adsorption of Cr(VI) using $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ was attributed to the sites provided by MgAl-LDH in the composite.

3.2 Effect of solution pH on Cr(VI) adsorption

Solution pH plays an important role in Cr(VI) adsorption owing to its effect not only on the

degree of speciation and ionization of Cr(VI) but also on surface charge of the adsorbent. Fig. 2 illustrated the results of Cr(VI) adsorption by CoFe₂O₄/MgAl-LDH with the initial solution pH ranging from 2.0 to 11.0 at initial Cr(VI) concentration of 50 mg/L. It was observed that the adsorbent can be quickly separated from the aqueous solution by an external magnet before and after adsorption process. The amount of Cr(VI) adsorbed on CoFe₂O₄/MgAl-LDH was highly pH dependent, and the q_e value decreased gradually from 16.4 to 1.2 mg/g with increasing solution pH from 2.0 to 11.0.

The result could be explained by the pH_{zpc} of the adsorbent, which was illustrated in Fig. S3. The corresponding pH value of the intersection point (intersection of the two curves of the pH_{final} versus $pH_{initial}$) was 8.8, i.e. the pH of the CoFe₂O₄/MgAl-LDH composite was 8.8. It is reported that Cr(VI) exists in species of H₂CrO₄, HCrO₄⁻, CrO₄²⁻, and Cr₂O₇²⁻ at different ratios in aqueous solution, depending on the pH of the system.^{3,14} At pH < 8.8, a lower solution pH caused the adsorbent surface to carry a positive charge due to protonation of the adsorbent surface,²² and thus would more significantly attract the anions of Cr(VI). Moreover, the predominant Cr(VI) species of HCrO₄⁻ was gradually converted to CrO₄²⁻ with an increase of solution pH. However, the adsorption free energy of HCrO₄⁻ (-2.5 to -0.6 kcal/mol) was higher than that of CrO₄²⁻ (-2.1 to -0.3 kcal/mol),³ thus HCrO₄⁻ was more favorable for adsorption than CrO₄²⁻. This could be further explained by the curve of the equilibrium pH versus the initial pH as depicted in Fig. 2, where the pH at equilibrium was found to be higher than the initial solution pH due to the decrease of H⁺ ions concentration by the formation of HCrO₄⁻ from CrO₄²⁻. At solution pH > 8.8, the surface of the adsorbent became negatively charged due to deprotonation. Thus electrostatic repulsion between the negatively charged Cr(VI) species and the negatively charged adsorption sites on the adsorbent would increase. This would result in a release of the adsorbed HCrO₄⁻ and CrO₄²⁻. Moreover, the competition of OH⁻ ions for adsorption sites with Cr(VI) species increased with the increase of pH, resulting in a decrease in Cr(VI) uptake. Fig. 2 showed that the equilibrium pH was lower than the initial pH in the alkaline solutions, which was attributed to the OH⁻ ions concentration decreased by competing for adsorption sites with CrO₄²⁻. Accordingly, pH value at 2 was an ideal parameter in this study.

3.3 Adsorption kinetics

Effect of initial concentration on Cr(VI) adsorption using CoFe₂O₄/MgAl-LDH was investigated by carrying out the experiments at different initial concentrations (50, 100 and 200 mg/L) and varying the contact time (Fig. 3). With increasing concentration from 50 to 200 mg/L, the equilibrium time increased from 90 to 300 min. As depicted in the figure, the adsorption rate was very high due to the availability of abundant adsorption sites on the surface of CoFe₂O₄/MgAl-LDH and the large concentration gradient between the fluid film around the adsorbent particle. After a lapse of time, the remaining vacant adsorption sites were difficult to be occupied because of repulsive forces between the Cr(VI) molecules on the solid and bulk phases, resulting in a low adsorption rate until the achievement of equilibrium. The uptake amount of Cr(VI) at equilibrium was observed to increase immensely from 16.24 to 54.37 mg/g with initial Cr(VI) concentration increased from 50 to 200 mg/L. High initial Cr(VI) concentration expanded the effective contact area with adsorbent and provided essential driving force to transcend the resistance to the mass transfer of Cr(VI) on interface.

To analyze the mechanism and rate-controlling step in the overall adsorption process of Cr(VI) onto CoFe₂O₄/MgAl-LDH, the experimental data was fitted using pseudo-first-order and pseudo-second-order kinetic models,^{36,37} with the respective kinetics equations defined as follows:

$$\log(q_e - q_t) = \log q_e - \frac{k_1}{2.303} \cdot t \quad (3)$$

$$\frac{t}{q_t} = \frac{1}{k_2 \cdot q_e^2} + \frac{1}{q_e} \cdot t \quad (4)$$

where q_e (mg/g) and q_t (mg/g) are the amounts of Cr(VI) adsorbed at equilibrium time and at any instant of time, t , respectively, k_1 (1/min) and k_2 (g/(mg min)) are the rate constant of pseudo-first-order and pseudo-second-order model, respectively. The values of k_1 and k_2 can be determined from the slope of the linear plot of $\log(q_e - q_t)$ versus t and t/q_t versus t , respectively.

Table 2 summarized the calculated kinetic parameters obtained by the linear regression for the two models (Fig. 4a and Fig. 4b). The correlation coefficient (R^2) obtained from the pseudo-second-order kinetic model ($R^2 > 0.999$) was higher than that obtained from the

pseudo-first-order kinetic model (R^2 was in the range of 0.9406-0.9721), suggesting that the adsorption of Cr(VI) onto CoFe₂O₄/MgAl-LDH could be well described by the pseudo-second-order kinetic model. Besides, the experimental equilibrium capacity ($q_{e,exp}$) were very close to the calculated equilibrium capacity ($q_{e,cal}$) for this model. The fitness of the pseudo-second-order kinetic model implied that the rate-limiting step may be chemical adsorption involving valency forces through sharing or exchange of electrons between the adsorbent and Cr(VI).³⁷ However at the same time, the initial rapid phase within the first 30 min may involve physical adsorption or exchange at the surface of the adsorbent.³⁶

The adsorption on a porous adsorbent will generally have multi-step process. The intraparticle diffusion model proposed by Weber and Morris was also used to characterize the adsorption data. The plot of q_t versus $t^{1/2}$ at different initial Cr(VI) concentrations was depicted in Fig. 4. As observed, the plot exhibited a multi-straight-line nature, suggesting that more than one process affected the adsorption. The values of k_i and R^2 were shown in Table 2. The data represented three periods of adsorption including the rapid section (stage 1 and stage 2) and the stabilization section (stage 3). The initial rapid stages were ascribed to the passage of Cr(VI) into the pores of CoFe₂O₄/MgAl-LDH corresponding to the boundary layer diffusion. The final stage was the residual adsorption process, indicating that the adsorption reached ultimate equilibrium. Additionally, Table 2 also represented that the rate constants ($k_{i,1}$, $k_{i,2}$ and $k_{i,3}$) increased significantly in all adsorption regions with increasing initial Cr(VI) concentration from 50 to 200 mg/L, suggesting that the driving force increased as the Cr(VI) concentrations was increased.

3.4 Adsorption isotherms and thermodynamic studies

Adsorption isotherms are usually used to describe the relationship between the adsorbate concentration in solution and the adsorbate amount adsorbed by the unit mass of adsorbent at a constant temperature at equilibrium. Equilibrium study in adsorption is fundamentally important for the predictive modeling procedures for analyzing and designing an adsorption system. Fig. 5 showed the effect of temperature on the uptake of Cr(VI) by CoFe₂O₄/MgAl-LDH. With increase in temperature from 283 to 323K, the adsorbed amount of Cr(VI) decreased gradually for all the concentrations. This may be attributed to desorption caused by an increased available thermal energy. Higher temperature induced higher mobility

of the solute causing desorption.³⁸ Moreover, a decrease in q_e value with an increase in temperature indicated an exothermic reaction nature of the adsorption. Similar trends were also reported by Sadaoui et al.³⁹ and Sadaoui et al.⁴⁰ It was found that the maximum adsorption capacities of Cr(VI) by micellar compounds decreased from 17.89 to 13.85 mg/g with increasing temperature from 30 to 45°C; Gupta et al. also reported that the uptake of Cr(VI) decreased from 14.7 to 12.8 mg/g with the rise in temperature from 303 to 323K (30 to 50°C).

To examine the relationship between Cr(VI) and the adsorbent at equilibrium and to search the maximum adsorption capacity of the adsorbent, the experimental data were analyzed by the well-known Langmuir and Freundlich isotherm models,⁴¹ which are usually expressed by the following equations:

$$q_e = \frac{b \cdot q_m \cdot C_e}{1 + b \cdot C_e} \quad (5)$$

$$q_e = K_f \cdot C_e^{1/n} \quad (6)$$

where q_e (mg/g) and C_e (mg/L) are the adsorption capacity and the equilibrium concentration of the adsorbate in solution, respectively, q_m (mg/g) is the maximum adsorption capacity corresponding to the complete monolayer coverage, b (L/mg) is the Langmuir constant related to the affinity of binding sites, and K_f and $1/n$ are Freundlich constants related to adsorption capacity and adsorption intensity, respectively.

The results obtained from the isotherms are summarized in Table 3. It was found that Langmuir model could be better described the adsorption process for the higher correlation coefficients ($R^2 > 0.99$) compared with Freundlich model, suggesting the homogeneous adsorption of Cr(VI) on CoFe₂O₄/MgAl-LDH and the adsorbed Cr(VI) formed a mono-molecular layer on the surface of the adsorbent. The maximum adsorption capacity of the adsorbent determined from the Langmuir model was found to be 72.4 mg/g for temperatures of 283 K. It is important to note that the adsorption capacity of Cr(VI) exhibited by the CoFe₂O₄/MgAl-LDH (72.4 mg/g) is higher than some other hydrotalcite materials such as uncalcined carbonate-Mg-Al LDHs (17 mg/g), Li/Al LDH (9.98 mg/g), calcined Mg-Al-Zr (24 mg/g), uncalcined Mg-Al LDHs (16.3 mg/g), HLCs (25.7 mg/g), calcined

MgAl-CO₃-HT (33.4-44.7 mg/g) and uncalcined chloride-Zn-Al LDHs (23.3 mg/g) (as shown in Table 4), which expressed a potential in the application of Cr(VI) removal. Decreasing in Langmuir constant b with temperature confirmed the exothermic nature of the adsorption process.

The essential characteristics of the Langmuir adsorption isotherm can be expressed by means of a dimensionless constant, R_L , which is referred to as separation factor or equilibrium parameter and can be defined as:

$$R_L = \frac{1}{1 + C_0 \cdot b} \quad (7)$$

The R_L value suggests the type of isotherm to be unfavorable ($R_L > 1$), linear ($R_L = 1$), favorable ($0 < R_L < 1$), irreversible ($R_L = 0$). From Table 3, the R_L values were found to be in the range of 0 to 1, suggesting the favorable adsorption of Cr(VI) on CoFe₂O₄/MgAl-LDH.

Thermodynamic consideration of an adsorption process are necessary to deduce whether the process is spontaneous or not, and provide in-depth information about internal energy changes that are associated with the adsorption. Experimental data of Cr(VI) adsorbed at equilibrium at different temperatures was used to evaluate the thermodynamic parameters such as enthalpy change (ΔH), Gibbs free energy change (ΔG), and entropy change (ΔS) for the adsorption system by the following equations:

$$\Delta G = -RT \ln K_L \quad (8)$$

$$\Delta G = \Delta H - T \cdot \Delta S \quad (9)$$

where K_L (L/mol) is the Langmuir constant. ΔH and ΔS can be calculated from the slope and intercept of van't Hoff plots of $\ln K_L$ versus $1/T$. The obtained ΔG , ΔH , and ΔS were listed in Table 5.

The negative values of ΔG at various temperatures (-1.14, -0.71 and -0.28 kJ/mol to 283, 303 and 323 K, respectively) demonstrated the feasibility and spontaneous nature of the adsorption process. The value of ΔG became more negative with the decrease in temperature, indicating that lower temperature facilitated adsorption of Cr(VI) onto CoFe₂O₄/MgAl-LDH. The negative value of ΔH (-7.18 kJ/mol) indicated that the reaction was exothermic; hence the uptake amount of Cr(VI) decreased with increasing temperature of

the solution. The negative value ΔS (-21.36 J/mol K) of Cr(VI) adsorption using CoFe₂O₄/MgAl-LDH corresponded to a decrease in randomness at the liquid/solid interface during the adsorption process.

3.5 Adsorption mechanisms

The adsorption experiments of CoFe₂O₄ for Cr(VI) were carried out, but it turned out that the CoFe₂O₄ had almost no adsorption capacity for Cr(VI) (data not shown). This result suggested that the adsorption of Cr(VI) using CoFe₂O₄/MgAl-LDH may be contributed to MgAl-LDH. To elucidate the interaction mechanisms between Cr(VI) ions and the adsorbent, FTIR analyses of MgAl-LDH, CoFe₂O₄, CoFe₂O₄/MgAl-LDH before and after Cr(VI) adsorption were performed.

The FTIR spectrum of MgAl-LDH showed characteristic bands related to the H-bonding stretching vibrations of OH groups in the brucite-like layer at 3441 cm⁻¹ and the H₂O bending vibration at 1637 cm⁻¹. A band at 1362 cm⁻¹ may be attributed to contamination by CO₃²⁻ ions in the MgAl-LDH synthesis.²¹ The bands between 400 and 800 cm⁻¹ could be related to the superposition of the characteristic vibrations of aluminum and magnesium oxides.²² Fig. 6b exhibited the FTIR spectrum of CoFe₂O₄. The adsorption peaks at 590 and 410 cm⁻¹ may be ascribed to the intrinsic vibration of the tetrahedral and octahedral sites in the CoFe₂O₄ particles.⁴⁷ However, the CoFe₂O₄ synthesized in this study did not show any bands related to the H-bonding stretching vibrations of the OH group, resulting in low adsorption capacity for Cr(VI). The FTIR spectrum of the CoFe₂O₄/MgAl-LDH composite illustrated in Fig. 6c was almost identical to that of the MgAl-LDH. As shown in Fig. 6d, the band at 3442 cm⁻¹ shifted to 3398 cm⁻¹ after adsorption of Cr(VI), suggesting that the bonded OH groups played an important role in Cr(VI) adsorption.⁴⁸ Additionally, the characteristic FTIR band of chromate due to mode $\nu_d(\text{Cr-O})$, recorded at 890 cm⁻¹ for free chromate,²² appeared at 880 cm⁻¹ for the CoFe₂O₄/MgAl-LDH sample after adsorption of Cr(VI). This indicated the interlayer NO₃⁻ ions were exchanged with Cr(VI) anions in solution.²¹ The slight shift toward lower frequency from 890 to 880 cm⁻¹ suggested that the Cr-O bond for CoFe₂O₄/MgAl-LDH-Cr was weaker than for the free chromate, which may be attributed to hydrogen bonding of the HCrO₄⁻ with layer OH groups and interlayer H₂O molecules.

In order to give more detailed information about the adsorption mechanism, MgAl-LDH,

CoFe₂O₄, CoFe₂O₄/MgAl-LDH before and after Cr(VI) adsorption were analyzed by the XPS. Compared to the typical XPS spectra of CoFe₂O₄ shown in Fig. S4, the wide scan XPS spectra of CoFe₂O₄/MgAl-LDH before and after Cr(VI) adsorption exhibited not only Co 2p, Fe 2p, O 1s peaks, but also Mg 1s and Al 2p peaks, which also verified the formation of LDHs phase in the CoFe₂O₄ nanocomposite. In addition, the new peak at about 580.0 eV was detected from Fig. 7b, suggesting that adsorption of Cr(VI) on the adsorbent. Fig. 7c illustrated the high-resolution spectrum of O 1s for the virgin adsorbent. Devolution of the peak O 1s of CoFe₂O₄/MgAl-LDH clearly showed three components at binding energy of 532.6, 531.7 and 530.6 eV. The first component at binding energy of 532.6 eV was assigned to chemically or physically adsorbed water.⁴⁹ The second one, at about 531.7 eV, corresponded to hydroxyl groups as also identified in several other adsorbents such as iron nanoparticles,⁴⁹ Al₃Mg₂,⁵⁰ and Mg-Fe-La composite⁵¹ at the same binding energy. The third one at binding energy of 530.6 eV was assigned to O²⁻ of Co, Fe, Mg and Al oxide (denoted as M-O, because Co, Fe, Mg and Al oxides could not be clearly separated).⁵¹ Notably, the intensity and O 1s components of the adsorbent had obvious changes after Cr(VI) adsorption (Fig. 7d). Compared with the virgin CoFe₂O₄/MgAl-LDH, the relative area ratio for the peak assigned to M-O increased from 22.29% to 36.25%. However, the relative area ratio for the peaks corresponding to H₂O and OH decreased from 30.20% to 25.56% and from 47.51% to 38.19%, respectively, and this further revealed that hydroxyl groups on the adsorbent surface participates in the adsorption of Cr(VI).

In conclusion, the adsorption of Cr(VI) onto CoFe₂O₄/MgAl-LDH involved both physical and chemical adsorption and could be speculated to occur in two ways. On one hand, Cr(VI) ions entered and were adsorbed into the pores of the CoFe₂O₄/MgAl-LDH composite through physical adsorption. On the other hand, as shown in Fig. 8, adsorption occurred at the adsorbent surface via electrostatic interaction between negative charged Cr(VI) ions and positively charged surface of the CoFe₂O₄/MgAl-LDH composite, forming an outer-sphere complex. Moreover, NO₃⁻ anions existing in interlayer of the adsorbent were exchanged with Cr(VI) anions through anion exchange.

3.6 Effect of coexisting ions

Investigations showed that the concentrations of coexistent cations and anions in industrial

wastewater containing Cr(VI) generated from electroplating, metal finishing, leather tanning, and pigment manufacturing varied from dozens to hundreds of milligrams per liter (mg/L). In this study, experiments were carried out to examine the effect of commonly present non-toxic ions such as Na^+ , K^+ , Ca^{2+} and Mg^{2+} ($C_0=2000\text{mg/L}$), on removal of Cr(VI) by $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$. It turned out that the presence of these kinds of cations have no significant influence on the removal efficiency of Cr(VI). As Cr(VI) exist in the form of anions in aqueous phase, and adsorption of Cr(VI) occurs at the adsorbent surface via electrostatic interaction and anion exchange in our study. Therefore, cations such as Na^+ , K^+ , Ca^{2+} and Mg^{2+} can not be adsorbed effectively by $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$.

Experiments were also performed to study the effect of commonly present anions such as NO_3^- , Cl^- , SO_4^{2-} and PO_4^{3-} ($C_0=200, 400, 800, 2000\text{mg/L}$) on Cr(VI) adsorption, and the results were depicted in Fig. 9. The removal of Cr(VI) using $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ was inhibited by the addition of SO_4^{2-} and PO_4^{3-} in the solution, however, the inhibition effect of Cl^- and NO_3^- on Cr(VI) removal was negligible even when the concentration of Cl^- and NO_3^- was increased up to 2000 mg/L. Anions of SO_4^{2-} and PO_4^{3-} are known to be adsorbed by forming firmly bonded inner-sphere complex with the hydroxyl groups at the surface of adsorbents, however, NO_3^- and Cl^- could only form outer-sphere complex^{52,53}. This indicated that Cr(VI) was adsorbed by forming inner-sphere complex on the surface of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$, and therefore SO_4^{2-} and PO_4^{3-} competed with Cr(VI) ions much better than NO_3^- and Cl^- .

3.7 Desorption and reusability study

To gain further insight into its actual application, the regeneration and reuse of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ was investigated using Na_2CO_3 (0.05 mol/L) as eluent (Fig. S5). From the figure, it was found that the adsorbed amount of Cr(VI) on $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ was still high in the sixth regeneration cycle, with 14.86 mg/g of Cr(VI) adsorption which decreased only by 9.5% compared with the adsorbed amount in first cycle, suggesting that the as-prepared adsorbent could be regenerated and reused effectively by Na_2CO_3 and could have the potential use in treatment of wastewater contaminated by Cr(VI).

4. Conclusions

Magnetic CoFe₂O₄/MgAl-LDH composite was successfully prepared, well characterized by SEM, BET, XRD, FTIR and XPS, and employed as an adsorbent for Cr(VI) removal. The result showed that the synthesized CoFe₂O₄/MgAl-LDH was a composite of CoFe₂O₄ and MgAl-LDH, and the combination was a physical process. The BET surface area and average pore diameter of the adsorbent were 120.75 m²/g and 18.85 nm, respectively. Batch adsorption experiments showed that the adsorption of Cr(VI) using CoFe₂O₄/MgAl-LDH was dependent on solution pH, contact time, initial concentration, temperature and coexisting anions. The adsorption kinetics followed pseudo-second-order kinetic equation. The equilibrium data could be fitted by the Langmuir isotherm, and the maximum adsorption capacity was found to be 72.4 mg/g for temperature of 25 °C. Thermodynamic studies revealed the exothermic and spontaneous nature of the adsorption process. Mechanism study indicated that Cr(VI) adsorption on CoFe₂O₄/MgAl-LDH not only included physical adsorption on the adsorbent surface, but also involved the chemical adsorption of complexation and ion exchange interaction. These results indicated that the prepared CoFe₂O₄/MgAl-LDH was an effective adsorbent for Cr(VI) removal with quick separation.

Acknowledgement

This work was financially supported by the National Science & Technology Pillar Program during the Twelfth Five-year Plan Period (2012BAJ24B03).

References

- [1] B. Deng and T. S. Alan, *Environ. Sci. Technol.*, 1996, **30**, 2484.
- [2] Y. Y. Sun, Q. Y. Yue, Y. P. Mao, B. Y. Gao; Y. Gao and L. H. Huang, *J. Hazard. Mater.*, 2014, **265**, 191.
- [3] C. Weng, J. Wang and C. Huang, *Water Sci. Technol.*, 1997, **35**, 55.
- [4] B. Chen, X. S. Zhao, Y. Liu, B. G. Xu and X. J. Pan, *RSC Adv.*, 2015, **5**, 1398.
- [5] V. Sarin and K. K. Pant, *Bioresource Technol.*, 2006, **97**, 15.
- [6] Ministry of Health, Sanitary Standard for Drinking Water, UDC 613.3/GB5749-2006, Ministry of Health, Beijing, 2006 (in Chinese).
- [7] R. C. Thomson and M. K. Miller, *Acta Mater.*, 1998, **46**, 2203.
- [8] S. Mustafa, K. H. Shah, A. Naeem, M. Waseem and M. Tahir, *J. Hazard. Mater.*, 2008, **160**, 1.
- [9] C. A. Kozlowski and W. Walkowiak, *Water Res.*, 2002, **36**, 4870.
- [10] E. Salazar, M. I. Oritiz, A. M. Urtiaga and J. A. Irabien, *Ind. Eng. Chem. Res.*, 1992, **31**, 1516.
- [11] J. N. Dui, G. Y. Zhu and S. M. Zhou, *ACS Appl. Mater. Inter.*, 2013, **5**, 10081.
- [12] Y. Chen, and G. Gu, *Bioresource Technol.*, 2005, **96**, 1713.
- [13] X. Jing, Y. Gao, X. Zhang, D. Wang, X. Wu, and H. Xu, *Desalination*, 2011, **269**, 120.
- [14] E. Demirbas, M. Kobya, E. Senturk and E. T. Ozkan, *Water SA*, 2004, **30**, 533.
- [15] S. J. Park and Y. S. Jang, *J. Coll. Interf. Sci.*, 2002, **249**, 458.
- [16] A. B. Albadarin, C. Mangwandi, G. M. Walker, S. J. Allen, M. N. M. Ahmada and M. Khraisheh, *J. Environ. Manage.*, 2012, **114**, 190.
- [17] M. Avila, T. Burks, F. Akhtar, M. Gothelid, P. C. Lansaker, M. S. Toprak, M. Muhammed and A. Uheida, *Chem. Eng. J.*, 2014, **245**, 201.
- [18] L. Wang, X. Xu, D. G. Evans, X. Duan and D. Li, *J. Solid State Chem.*, 2010, **183**, 1114.
- [19] D. G. Evans and R. C. T. Slade, *Struct. Bond.*, 2006, **119**, 1.
- [20] S. L. Wang, R. J. Hseu, R. R. Chang, P. N. Chiang, J. H. Chen and Y. M. Tzou, *Colloids Surf., A*, 2006, **277**, 8.
- [21] Y. J. Li, B. Y. Gao, T. Wu, D. J. Sun, X. Li, B. Wang and F. J. Lu, *Water Res.*, 2009, **43**, 3067.
- [22] T. Kameda, E. Kondo and T. Yoshioka, *Sep. Purif. Technol.*, 2014, **122**, 12.
- [23] W. W. Wang, J. B. Zhou, G. Achari, J. G. Yu and W. Q. Cai, *Colloids Surf., A*, 2014, **457**, 33.
- [24] K. H. Goh, T. T. Lim and Z. L. Dong, *Water Res.*, 2008, **42**, 1343.
- [25] L. Deng, Z. Shi, B. Li, L. F. Yang, L. Luo and X. Z. Yang, *Ind. Eng. Chem. Res.*, 2014, **53**, 7746.
- [26] R. R. Shan, L. G. Yan, K. Yang, S. J. Yu, Y. F. Hao, H. Q. Yu and B. Du, *Chem. Eng. J.*, 2014, **252**, 38.
- [27] L. C. A. Oliveira, R. V. R. A. Rios, J. D. Fabris, V. Garg, K. Sapag and R. M. Lago, *Carbon*, 2002, **40**, 2177.
- [28] P. F. Wang, M. H. Gao, C. Wang, Y. H. Ao, J. Hou and J. Qian, *Appl. Surf. Sci.*, 2014, **290**, 116.

- [29] A. Mohammadi, H. Daemi and M. Barikani, *Int. J. Biol. Macromol.*, 2014, **69**, 447.
- [30] X. B. Fang, Z. Q. Fang, P. K. E. Tsang, W. Cheng, X. M. Yan and L.C. Zheng, *Appl. Surf. Sci.*, 2014, **314**, 655.
- [31] S. Z. Li, Y. B. Gong, Y. C. Yang, C. He, L. L. Hu, L. F. Zhu, L. P. Sun and D. Shu, *Chem. Eng. J.*, 2015, **260**, 231.
- [32] B. Tanhaei, A. Ayati, M. Lahtinen and M. Sillanpää, *Chem. Eng. J.*, 2015, **259**, 1.
- [33] J. Hu, I. M. C. Lo, and G. H. Chen, *Langmuir*, 2005, **21**, 11173.
- [34] A. Pirouzfard and S. A. Seyyed Ebrahimi, *J. Magn. Magn. Mater.*, 2014, **370**, 1.
- [35] U. Costantino, F. Marmottini, M. Nocchetti and R. Vivani, *Eur. J. Inorg. Chem.*, 1998, **1998**, 1439.
- [36] L. W. Low, T. T. Teng, A. Ahmad, N. Morad, Y. S. Wong, *Water Air Soil Pollut.*, 2011, **218**, 293.
- [37] Y. S. Ho and G. McKay, *Process Biochem.*, 1999, **34**, 451.
- [38] S. S. Baral, S. N. Das and P. Rath, *Biochem. Eng. J.*, 2006, **31**, 216.
- [39] Z. Sadaoui, S. Hemidouche and O. Allalou, *Desalination*, 2009, **249**, 768.
- [40] V. K. Gupta, A. Rastogi, A. Nayak, *J. Coll. Interf. Sci.*, 2010, **342**, 135.
- [41] Q. Cao, F. Huang, Z. Zhuang and Z. Lin, *Nanoscale*, 2012, **4**, 2423.
- [42] N. N. Das, J. Konar, M. K. Mohanta and S. C. Srivastava, *J. Coll. Interf. Sci.*, 2004b, **270**, 1.
- [43] E. Alvarez-Ayuso and H. W. Nugteren, *Water Res.*, 2005, **39**, 2535.
- [44] E. Ramos-Ramírez, N. L. Gutiérrez Ortega, C. A. Contreras Soto and M. T. Olguín Gutiérrez, *J. Hazard. Mater.*, 2009, **172**, 1527.
- [45] Y. F. Xu, J. Zhang, G. G. Qian, Z. P. Ren, Z. P. Xu, Y. Y. Wu, Q. Liu and S. Z. Qiao, *Ind. Eng. Chem. Res.*, 2010, **49**, 2752.
- [46] B. Hourri, A. Legrouri, A. Barroug, C. Forano and J. P. Besse, *Collect. Czech. Chem. C.*, 1998, **63**, 732.
- [47] H. Liu, F. Xu, L. C. Li, Y. P. Wang and H. Z. Qiu, *React. Funct. Polym.* 2009, **69**, 43.
- [48] H. H. Najafabadi, M. Irani, L. R. Rad, A. H. Haratameh and I. Haririan, *RSC Adv.*, 2015, **5**, 16532.
- [49] X. Q. Li and W. X. Zhang, *Langmuir*, 2006, **22**, 4638.
- [50] M. Liu, P. Schmutz, S. Zanna, A. Seyeux, H. Ardelean, G. Song, A. Atrens and P. Marcus, *Corros. Sci.*, 2010, **52**, 562.
- [51] J. Wang, D. J. Kang, X. L. Yu, M. F. Ge and Y. T. Chen, *Chem. Eng. J.*, 2015, **264**, 506.
- [52] C. H. Weng, C. Z. Tsai, S. H. Chu and Y. C. Sharma, *Sep. Purif. Technol.* 2007, **54**, 187.
- [53] G. Lefèvre, *Adv. Colloid Interface Sci.* 2004, **107**, 109.

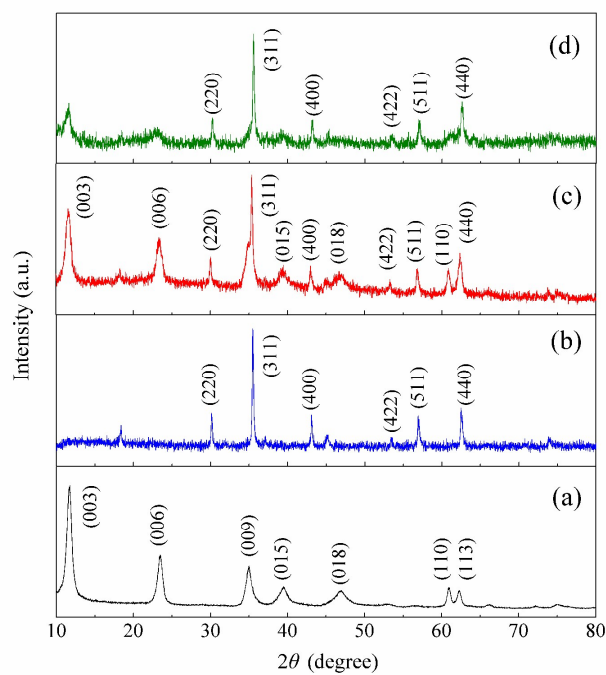


Fig. 1 XRD patterns of (a) MgAl-LDH, (b) CoFe₂O₄, (c) CoFe₂O₄/MgAl-LDH, and (d) CoFe₂O₄/MgAl-LDH after Cr(VI) adsorption.

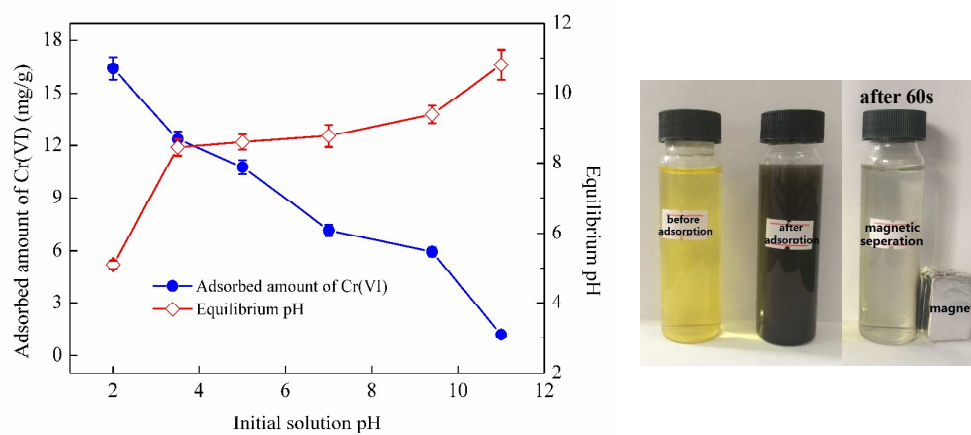
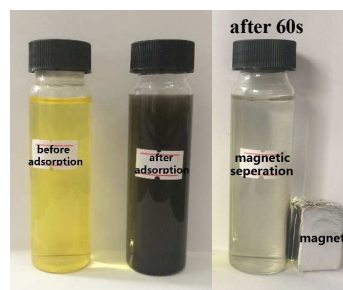


Fig. 2 Effect of initial solution pH on Cr(VI) adsorption and equilibrium pH using CoFe₂O₄/MgAl-LDH.



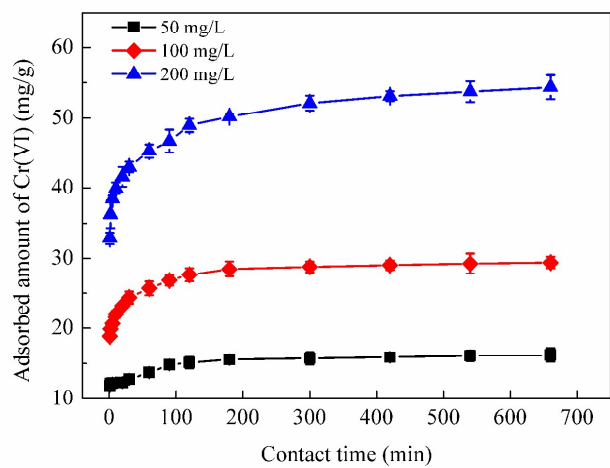


Fig. 3 Effect of contact time on Cr(VI) adsorption using CoFe₂O₄/MgAl-LDH for initial Cr(VI) concentrations of 50, 100 and 200 mg/L.

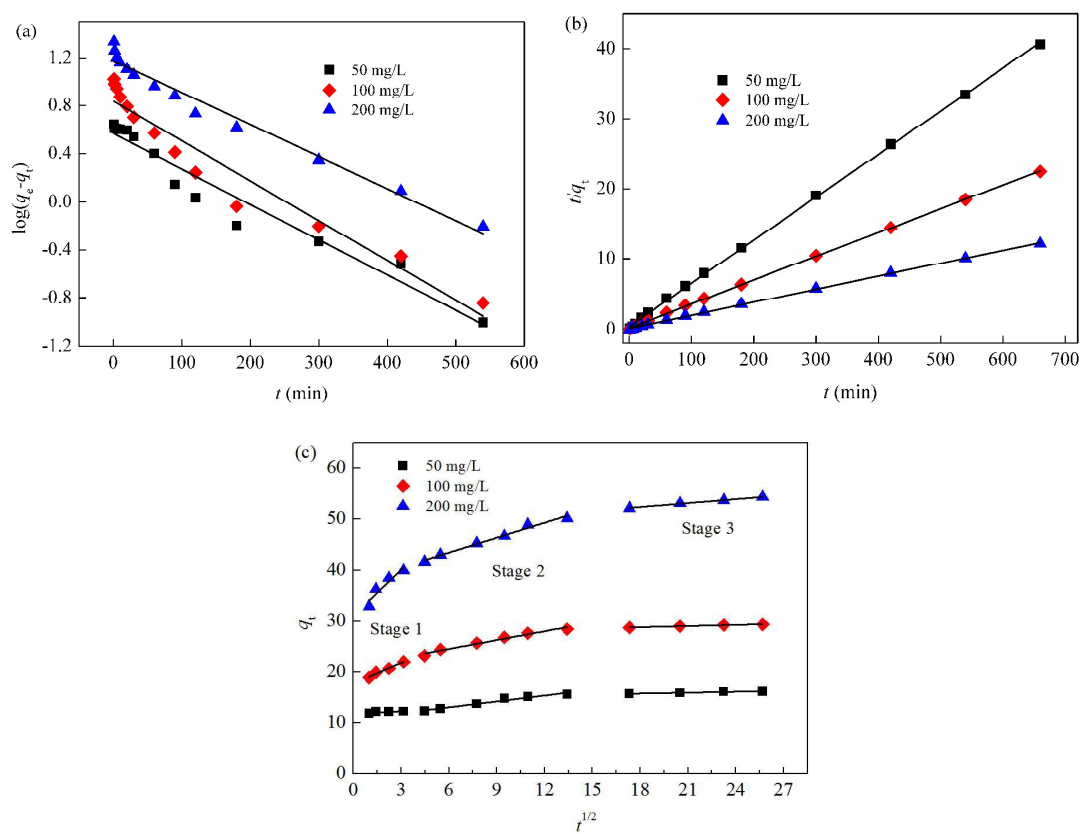


Fig. 4 Intraparticle diffusion model fitting of adsorption kinetic of Cr(VI) on CoFe₂O₄/MgAl-LDH.

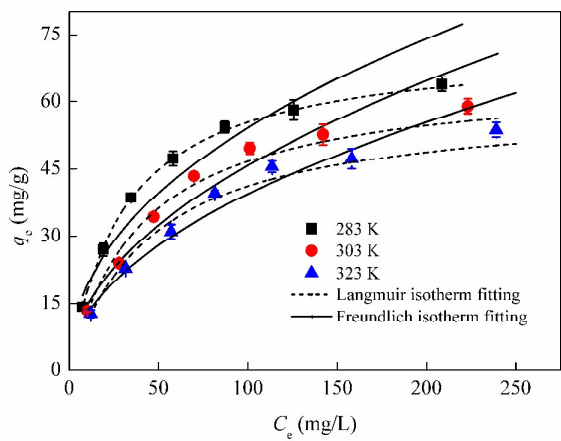


Fig. 5 Adsorption isotherm of Cr(VI) on CoFe₂O₄/MgAl-LDH at temperatures of 283, 303, 323 K.

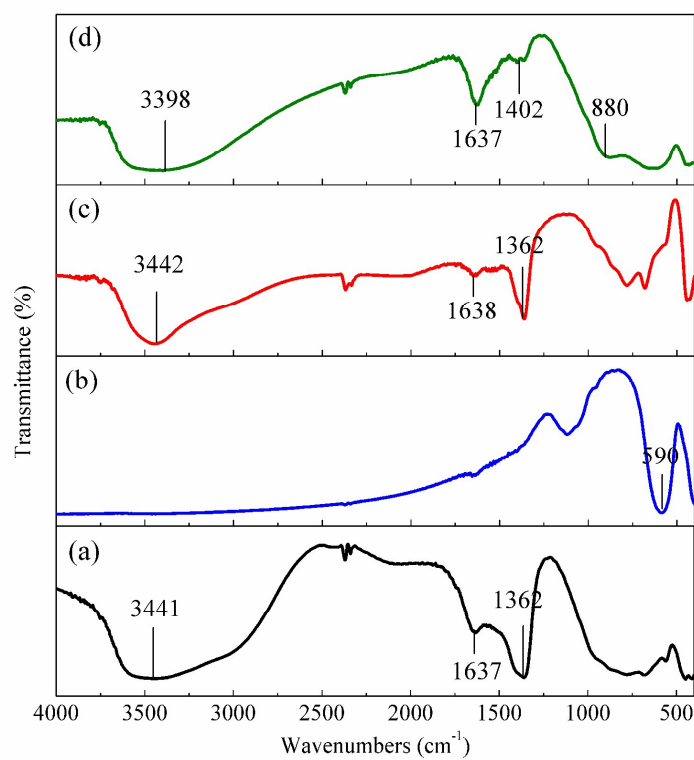


Fig. 6 FTIR spectra of (a) MgAl-LDH , (b) CoFe₂O₄, (c) CoFe₂O₄/MgAl-LDH, (d) CoFe₂O₄/MgAl-LDH after Cr(VI) adsorption.

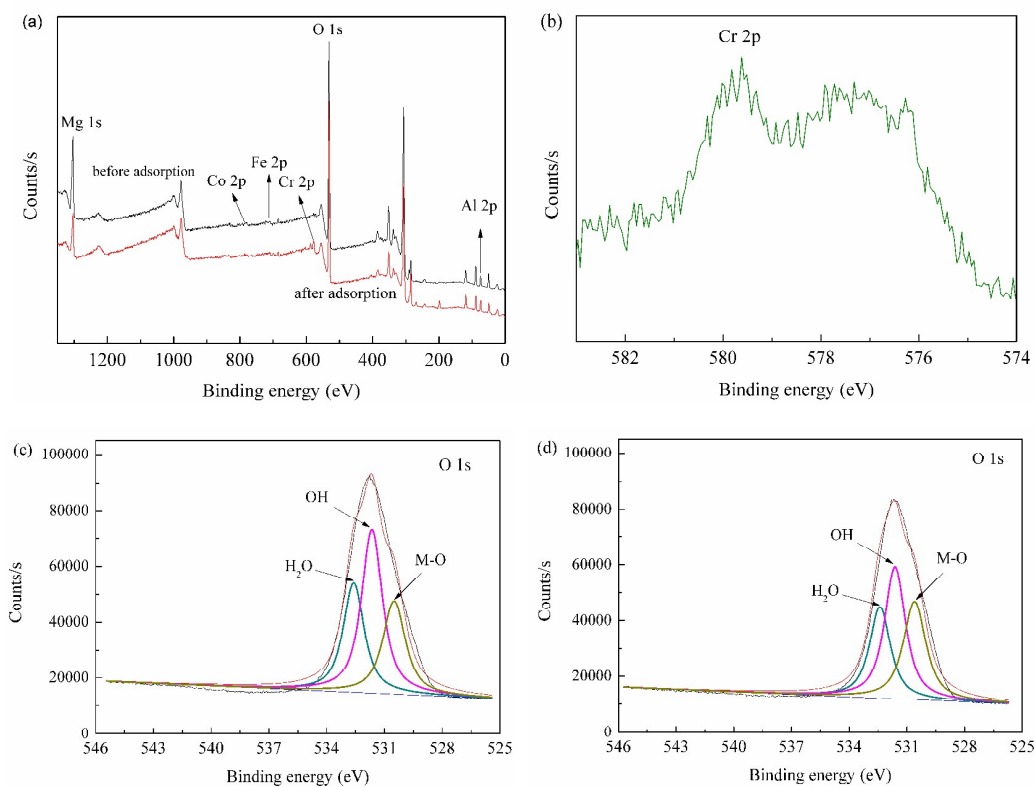


Fig. 7 Wide XPS spectra of (a) $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ before and after Cr(VI) adsorption, (b) Cr 2p spectrum of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ after Cr(VI) adsorption, (c) O 1s spectrum of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$, and (d) O 1s spectrum of $\text{CoFe}_2\text{O}_4/\text{MgAl-LDH}$ after Cr(VI) adsorption.

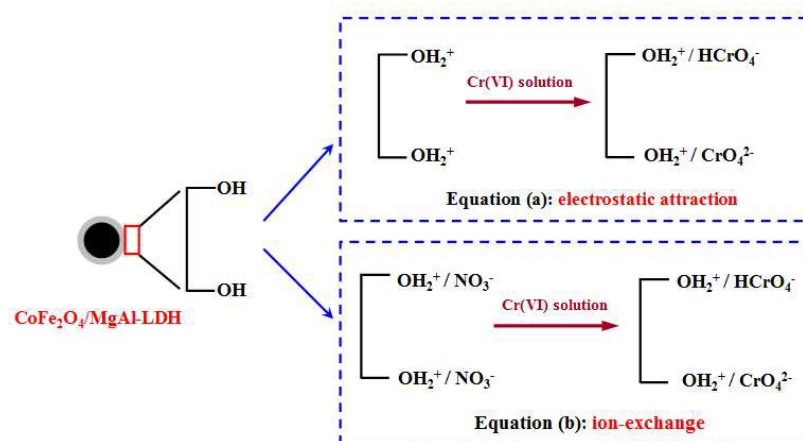


Fig. 8 Schematic illustration of the adsorption mechanism of Cr(VI) on CoFe₂O₄/MgAl-LDH.

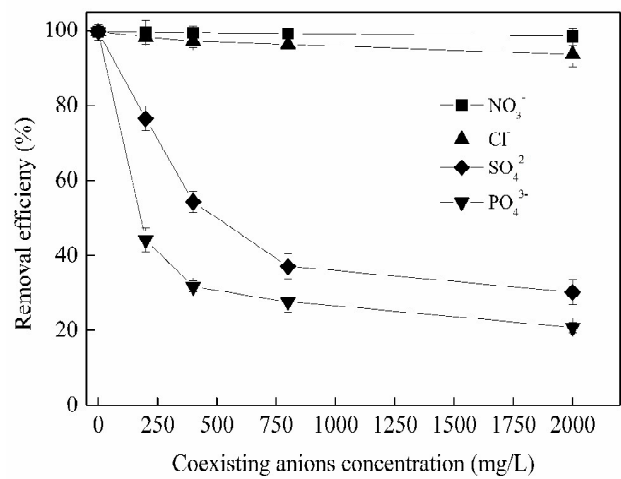


Fig. 9. Effect of coexisting anions on adsorption of Cr(VI) on CoFe₂O₄/MgAl-LDH.

Table 1 Comparison of BET surface areas, pore volumes and pore diameters of MgAl-LDH, CoFe₂O₄, CoFe₂O₄/MgAl-LDH, CoFe₂O₄/MgAl-LDH after Cr(VI) adsorption.

Adsorbent	BET surface area (m ² /g)	Pore volume (cc/g)	Average pore diameter (nm)
MgAl-LDH	143.60	0.963	15.48
CoFe ₂ O ₄	15.12	0.074	3.83
CoFe ₂ O ₄ /MgAl-LDH	120.75	0.756	18.85
CoFe ₂ O ₄ /MgAl-LDH after Cr(VI) adsorption	7.23	0.020	5.42

Table 2 Comparison of rate constants calculated based on respective pseudo-first-order, pseudo-second-order, and intraparticle diffusion kinetic models.

C_0	$q_{e,exp}$	Pseudo-first-order			Pseudo-second-order			Intraparticle diffusion					
		k_1	$q_{e,cal}$	R^2	k_2	$q_{e,cal}$	R^2	$k_{i,1}$	R_1^2	$k_{i,2}$	R_2^2	$k_{i,3}$	R_3^2
50	16.23	0.0046	3.68	0.9475	0.0106	16.26	0.9997	0.47	0.4925	0.39	0.9512	0.059	0.9844
100	29.40	0.0076	6.89	0.9406	0.0066	29.49	0.9998	1.34	0.9707	0.59	0.9702	0.076	0.9914
200	54.37	0.0060	14.96	0.9721	0.0024	54.41	0.9993	3.03	0.8328	0.99	0.9814	0.26	0.9924

Table 3 Parameters of Langmuir and Freundlich isotherms for adsorption of Cr(VI) onto CoFe₂O₄/MgAl-LDH.

T (K)	Langmuir isotherm				Freundlich isotherm		
	q_m (mg/g)	K_L (L/mg)	R_L	R^2	K_f (mg/g)	$1/n$	R^2
283	72.4	0.032	0.0725-0.385	0.9995	6.76	0.452	0.9440
303	65.7	0.024	0.0943-0.455	0.9908	4.64	0.496	0.9641
323	59.8	0.022	0.102-0.476	0.9929	4.05	0.494	0.9720

Table 4 The Cr(VI) adsorption capacity of CoFe₂O₄/MgAl-LDH compared with other hydrotalcite materials.

Adsorbent	Adsorption capacity (mg/g)	Reference
Uncalcined carbonate-Mg-Al LDHs	17	3
Li/Al LDH	9.98	21
Calcined Mg-Al-Zr (450°C)	24	42
Uncalcined Mg-Al LDHs	16.3	43
HLCs	25.7	
HLCs heated at 350°C	25.8	44
HLCs heated at 150°C	28.5	
Calcined MgAl-CO ₃ -HT (CHT)	33.4-44.7	45
Uncalcined chloride-Zn-Al LDHs	23.3	46
CoFe ₂ O ₄ /MgAl-LDH	72.4	This work

Table 5 Values of thermodynamic parameters for adsorption of Cr(VI) onto CoFe₂O₄/MgAl-LDH.

T (K)	$\ln K_L$	ΔG (kJ/mol)	ΔH (kJ/mol)	ΔS (J/mol K)
283	0.509	-1.14	-7.18	-21.36
303	0.222	-0.71		
323	0.135	-0.28		