

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Enhanced Removal of Diclofenac from Water
using Zeolitic Imidazole Framework functionalized
with Cetyltrimethylammonium Bromide (CTAB)

Kun-Yi Andrew Lin^{a,}, Hongta Yang^b and Wei-Der Lee^a*

^a Department of Environmental Engineering;

^b Department of Chemical Engineering, National Chung Hsing University

250 Kuo-Kuang Road, Taichung, Taiwan, R.O.C.

*Corresponding Author. Tel: +886-4-22854709, E-mail address: linky@nchu.edu.tw

(Kun-Yi Andrew Lin)

Abstract

Diclofenac represents one of the most common pharmaceuticals and personal care products (PPCPs) in municipal wastewater. To enhance the removal of diclofenac from water, a cationic surfactant, cetyltrimethylammonium bromide (CTAB), was introduced into zeolitic imidazole framework (ZIF)-67. CTAB is added originally to minimize use of ligand during the synthesis of ZIF-67; however CTAB present in ZIF-67 also increases surface charge and thus enhances adsorption capacity up to 10 times compared to CTAB-free ZIF-67. Factors influencing the diclofenac adsorption are investigated, including CTAB loading, temperature and pH. A loading of 0.274 mol-CTAB/mol-Co²⁺ is suggested as an optimal loading to prepare a relatively efficient CTAB-ZIF-67, while over loading of CTAB could not fully incorporate CTAB into ZIF-67. In view of the diclofenac adsorption kinetics and isotherm, the adsorption of diclofenac to CTAB-ZIF-67 was considered to involve a strong affinity between diclofenac and CTAB-ZIF-67 owing to the electrostatic attraction between the carboxylic acid of diclofenac and the quaternary amine of CTAB. Considering that the removal of diclofenac from urine is of great interests, separation of diclofenac from urine using CTAB-ZIF-67 was evaluated and also employed to investigate effect of co-existing ions. We also determined desorption behavior of diclofenac from CTAB-ZIF-67 to provide insight for recyclability of CTAB-ZIF-67 for the diclofenac adsorption.

Keywords: Zeolitic imidazole frameworks (ZIFs), ZIF-67, diclofenac, cetyltrimethylammonium bromide (CTAB)

1. Introduction

Emerging pollutants have become one of the most important issues in wastewater treatment. These emerging contaminants include pharmaceuticals and personal care products (PPCPs), flame retardants, pesticides, disinfection by-products, artificial and natural hormones¹. PPCPs particularly attract attention because they are highly persistent and low-biodegradable². Thus, PPCPs and their metabolic derivatives can be detected not only in effluents from wastewater treatment plants (WWTPs) but also surface water, ground water and even drinking water^{3,4}. The presence of PPCPs in various water bodies, even at trace levels, poses a serious threat to public health and the aqua ecology^{5,6}. Among these PPCPs, diclofenac appears to be one of the most concerning compounds because it has been extensively-used as a non-steroidal anti-inflammatory drug (NSAID) and commonly found in influents and effluents of WWTPs as well as drinking water^{4,7}. It is also considered to be harmful to aqua lives as well as vultures^{8,9}. Thus, it is necessary to eliminate diclofenac contamination in water.

Since conventional municipal WWTPs cannot effectively degrade diclofenac, advanced oxidation processes (AOPs) have been proposed to treat diclofenac in water¹⁰⁻¹². Nevertheless, oxidants (*e.g.*, ozone and peroxide) must be continuously spent and therefore it can be challenging to use AOPs to remove diclofenac in a large-scale operation¹³. Besides, derivatives from AOPs may exhibit even higher toxicity compared to the original pollutant⁴. Therefore, adsorption is still considered as a preferable approach to remove diclofenac from water considering its simplicity, low initial cost¹⁴, and by-product-free operation¹. To expand spectrum of adsorbent selection, recently a new type of inorganic-organic hybrid materials, so-called Metal Organic Frameworks (MOFs), has been developed. MOFs have been extensively used

in adsorption applications, such as CO₂ capture¹⁵⁻¹⁷, gas storage¹⁸, drug delivery¹⁹, and sensors²⁰. Considering successful demonstrations of MOFs in the above-mentioned areas, lately MOFs are also used to remove pollutants from aqueous solutions²¹⁻²³. Some MOFs are even proven to be promisingly advantageous than conventional sorbents for removal of pollutants from water^{21,24}. Thus, elimination of contaminants using MOFs has attracted increasing attention. Among various types of MOFs, Zeolitic Imidazole Frameworks (ZIFs) stand out as an intriguing subset because ZIFs exhibit superior thermal and chemical stabilities in aqueous solutions, even under alkaline conditions²⁵. ZIFs have been also employed to remove several pollutants such as humic acid²⁶, toxic dyes^{24,27}, and herbicides²³. Therefore, ZIFs should be a feasible adsorbent to remove diclofenac from water. However, to our best knowledge, few studies have evaluated the removal of diclofenac from water using ZIFs. Therefore, in this study ZIFs are employed to remove diclofenac from water. ZIF-67 was selected as a representative ZIF to remove diclofenac because ZIF-67 can be easily prepared under a mild condition in water. Considering that diclofenac is an acid (*i.e.*, 2-(2,6-dichloranilino) phenylacetic acid), surface-functionalization (*i.e.*, positively-charged modification) of ZIF-67 may facilitate the adsorption of diclofenac. Lately, ZIF-67 synthesized with assistance of surfactants has been demonstrated. The addition of surfactants (*i.e.*, cetyltrimethylammonium bromide (CTAB) and Pluronic F127) can minimize dosage of the ligand (*i.e.*, 2-methylimidazole) and allow the synthesis to proceed at room temperature with very high yield²⁸. In particular, the addition of CTAB, a cationic surfactant, in fact not only improves the synthesis but also incorporates the cationic group into ZIF-67. Thus, the presence of CTAB in ZIF-67 is expected to enhance the diclofenac adsorption. To examine the effect of CTAB addition, ZIF-67 was synthesized with different CTAB loadings to from

CTAB-ZIF-67. CTAB-ZIF-67 crystals were characterized using scanning electron microscopy (SEM), powder X-ray diffraction (PXRD), adsorption FT-IR as well as thermogravimetric analyzer (TGA). A pristine ZIF-67 (*i.e.*, CTAB-free ZIF-67) was also prepared to compare with CTAB-ZIF-67 in terms of diclofenac adsorption. Factors influencing the diclofenac adsorption were investigated, including CTAB loading, temperature and pH. An optimal CTAB loading was also suggested to prepare a relatively efficient CTAB-ZIF-67. The diclofenac adsorption kinetics and isotherm were obtained and analyzed using theoretical models. Thermodynamic parameters of the diclofenac adsorption were also determined to better understand the adsorption mechanism. Separation of diclofenac from urine using CTAB-ZIF-67 was evaluated to investigate effect of co-existing ions. We also determined desorption behavior of diclofenac from CTAB-ZIF-67 to provide insight for recyclability of CTAB-ZIF-67 for the diclofenac adsorption.

2. Experimental

2.1 Materials

Chemicals used in this study are all purchased from major suppliers and used without purification. Cobalt nitrate hexahydrate ($\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$) was obtained from Choneye Pure Chemicals (Taiwan). 2-methylimidazole (2-MIM) and CTAB were obtained from Acros Organics (USA). Sodium diclofenac (see Fig. S1 for its chemical structure) and nonionic triblock copolymer Pluronic F127 were purchased from Sigma-Aldrich. Ammonium hydroxide solution was obtained from Showa Chemicals (Japan). Deionized (DI) water was prepared to exhibit less than 18 M Ω cm. In this study, we also evaluated the separation of diclofenac from urine using CTAB-ZIF-67. The synthetic human urine was prepared according to the reported composition²⁹

which consists of 3 g L⁻¹ (0.050 M) of urea (Sigma-Aldrich, USA), 2.57 g L⁻¹ (0.044 M) of sodium chloride (Showa chemicals, Japan), 2.13 g L⁻¹ (0.015 M) of sodium sulfate (Showa chemicals, Japan), 2.98 g L⁻¹ (0.04 M) of potassium chloride (Showa chemicals, Japan), 0.81 g L⁻¹ (0.004 M) of magnesium chloride hexahydrate (Sigma-Aldrich, USA), 0.04 (or 1.41) g L⁻¹ (0.0003 M or 0.01 M) of sodium monohydrogen phosphate heptahydrate (Sigma-Aldrich, USA) and 0.58 g L⁻¹ (0.004 M) of calcium chloride dihydrate (Showa chemicals, Japan).

2.2 Synthesis and Characterization of CTAB-ZIF-67

CTAB-ZIF-67 was synthesized according to the reported procedure²⁸ as illustrated in Fig. 1. First, 1 g of 2-MIM (12.1 mmol), 0.15 g (0.032 mmol) of nonionic triblock copolymer, Pluronic F127 and 0.1 g (0.27 mmol) of CTAB were added to 30 ml of DI water, followed by 6.3 ml of ammonium hydroxide solution. On the other hand, 1.77 g (6.1 mmol) of Co(NO₃)₂·6H₂O was added to another beaker containing 30 ml of DI water. Next, the surfactant solution was slowly added to the cobalt solution, and the mixture was then stirred at ambient temperature for 8 hr. The resultant precipitate was collected by centrifugation and washed thoroughly with DI water, and dried at 60 °C in the ventilation oven for 6 hr and subsequently in the vacuum oven at 140 °C for 12 hr to obtain the final product. In this study, CTAB dosage was varied to prepare ZIF-67 with different CTAB-loadings. The CTAB-ZIF-67 prepared above (*i.e.*, 0.1 g (0.27 mmol) of CTAB) was denoted as CTAB-ZIF-67-M, represent its “moderate” CTAB dosage. CTAB-ZIF-67-L and CTAB-ZIF-67-H were synthesized using 0.05g (0.137 mmol) and 0.25 g (0.685 mmol) of CTAB to represent “low” and “high” CTAB loadings, respectively.

The as-synthesized CTAB-ZIF-67 was first characterized using a field emission SEM (JEOL JSM-6700, Japan) to observe its morphology. XRD patterns of CTAB-ZIF-67 were determined by an X-ray diffractometer (PANalytical, the Netherlands). Infrared (IR) spectrum of CTAB-ZIF-67 was obtained using a Fourier-Transform Infrared spectrometer (4100, Jasco, Japan). Thermal stability of CTAB-ZIF-67 was measured by a thermogravimetric analyzer (TGA i1000, Instrument Specialists Incorporated, USA) at a heating rate of 20 °C min⁻¹ from 25 to 800 °C in nitrogen. Zeta potentials of CTAB-ZIF-67 were obtained in water with pH varied from 3–11 using a zetasizer (Nano-ZS, Malvern Instruments Ltd, Malvern, UK).

2.3 Removal of diclofenac from water using CTAB-ZIF-67

Adsorption of diclofenac to CTAB-ZIF-67 was investigated by batch-type experiments. First, the adsorption kinetics was measured by adding 0.01 g of CTAB-ZIF-67 to a glass vial containing 0.02 L of diclofenac solution with an initial concentration $C_0 = 20 \text{ mg L}^{-1}$. The vial was immediately placed on the temperature-controllable orbital shaker at 300 rpm to increase contact between CTAB-ZIF-67 and diclofenac. The adsorption capacity of CTAB-ZIF-67 at different mixing time, $q_t \text{ (mg g}^{-1}\text{)}$, was calculated as follows (Eq. (1)):

$$q_t = \frac{V(C_0 - C_t)}{m} \quad (1)$$

where $m \text{ (g)}$ is the weight of CTAB-ZIF-67 added to the diclofenac solution. $V \text{ (L)}$ denotes the volume of the diclofenac solution, whereas C_t represents the remaining concentration of diclofenac at a mixing time t , which was analyzed using a UV spectrophotometer (E-chrome CT-200, Taiwan) at 276 nm according to the reported studies^{29, 30}. The adsorption capacity at equilibrium was defined as $q_e \text{ (mg g}^{-1}\text{)}$. To

estimate the maximal adsorption capacity of CTAB-ZIF-67, the adsorption isotherm of diclofenac to CTAB-ZIF-67 was measured using 0.01 g of CTAB-ZIF-67 with diclofenac solutions of increasing concentrations from 0 to 40 mg L⁻¹. Experiments of the adsorption kinetics and isotherm were also conducted at 20, 30 and 40 °C to examine effect of temperature. In this study, adsorption experiments were duplicated and repeated at least twice.

2.4 Effects of pH and co-existing ions on the adsorption of diclofenac

To investigate effect of pH, pH of diclofenac solutions was adjusted by adding 0.1 M of hydrochloric acid and sodium hydroxide to 4-10. Since diclofenac wastewater may also contain other compounds, it is critical to examine whether co-existing ions affect the diclofenac adsorption. Recently, the separation of diclofenac from urine has attracted great attention ²⁹ because around 70% of used pharmaceuticals were discharged in human urine as active drugs and metabolites ³¹. Thus, we particularly evaluated whether CTAB-ZIF-67 can separate diclofenac from urine and also examine whether ingredients in urine (*e.g.*, salts, urea and anions) can interfere with the diclofenac adsorption. Since urine typically contains high concentration of phosphate, variation of phosphate was also monitored during the diclofenac adsorption.

2.5 Recyclability and desorption of diclofenac from CTAB-ZIF-67

The recyclability of CTAB-ZIF-67 was also evaluated by regenerating the spent CTAB-ZIF-67 with concentrated sodium chloride solution (5 wt%) and an ion-exchange (I.E.) resin (Dowex Marathon C, strongly acidic). Desorption behaviors of diclofenac from CTAB-ZIF-67 in the presence of sodium chloride and the I.E. resin

were measured to provide insights to the recyclability. To obtain the desorption kinetics, diclofenac-saturated CTAB-ZIF-67 was added to a glass vial containing the concentrated sodium chloride solution (5 wt%) or the I.E. resin (5 wt%). Sample aliquots were withdrawn from the mixture and the concentration of diclofenac in the bulk phase was analyzed using the spectrophotometer. Surface areas and pore volumes of ZIF-67 samples were measured by a volumetric sorption analyzer (Micromeritics ASAP 2020, USA) at a relative pressure (P/P_0) range of 0.0001–0.99. The release of Co^{2+} from CTAB-ZIF-67 during the adsorption and desorption processes was determined by an atomic absorption spectrophotometer (Perkin Elmer AA100, USA).

3. Results and Discussion

3.1 Characterization of CTAB-ZIF-67

Morphologies of CTAB-ZIF-67 with various CTAB loadings can be seen in Fig. S2 (see ESI†), in which the morphology of ZIF-67 without CTAB loading is also revealed for comparison. It can be seen that the pristine ZIF-67 (w/o CTAB) (Fig. S2(a)) exhibited a well-developed chamfered-cubic structure with sharp edges. In the case of CTAB-ZIF-67-L (Fig. S2(b)), the chamfered-cubic morphology can be still observed, even though edges of the crystals were slightly rounded. Once the CTAB loading increased to form CTAB-ZIF-67-M (Fig. S2(c)), the edges were blunted. With the highest loading of CTAB, the morphology of CTAB-ZIF-67-H (Fig. S2(d)) started becoming irregular. Particle sizes were also found to become smaller with a higher CTAB loading. Similar morphological changes were observed when the addition of CTAB was increased^{28,32}. To examine whether the morphology variation and the addition of CTAB affected crystalline of CTAB-ZIF-67, the pristine ZIF-67

and CTAB-ZIF-67 with different CTAB loadings were analyzed by XRD and the result can be seen in Fig. 2(a). The XRD pattern of the pristine ZIF-67 can be readily indexed according to reported literatures³³: 7.31° (0 1 1), 10.36° (0 0 2), 12.72° (1 1 2), 14.40° (0 2 2), 16.45° (0 1 3), 18.04° (2 2 2), 22.15° (1 1 4), 24.53° (2 3 3), 25.62° (2 2 4), 26.70° (1 3 4), 29.67° (0 4 4), 30.62° (3 3 4), 31.55° (2 4 4) and 32.43° (2 3 5). This indicates that the as-synthesized pristine ZIF-67 was well-developed. Once CTAB was loaded in ZIF-67 to form CTAB-ZIF-67, CTAB-ZIF-67, regardless of the CTAB loading, exhibited comparable XRD patterns to that of the pristine ZIF-67. This indicates that even though CTAB was added to ZIF-67, its crystallinity could be still well-developed. The addition of CTAB, however, can be revealed using FT-IR (Fig. 2(b)). In the spectrum of the pristine ZIF-67, most of peaks are derived from its ligand (*e.g.*, 2-MIM). The peaks in the range of $600\text{--}1500\text{ cm}^{-1}$ could be attributed to the stretching and bending modes of the imidazole ring. The peak at 1584 cm^{-1} was due to the stretching mode of C=N bonding in 2-MIM. The peaks at 2929 and 3135 cm^{-1} were assigned to the stretching mode of C-H from the aromatic ring and the aliphatic chain in 2-MIM, respectively^{24, 33-35}.

Once CTAB was added to ZIF-67, spectra of CTAB-ZIF-67 are found to be similar to that of the pristine ZIF-67, except that a few additional peaks can be observed in the range of $2800\text{--}3000$ and 1378 cm^{-1} . In comparison with the spectrum of CTAB (Fig. 2(b)), these additional peaks can be attributed to CTAB: the peak at 1378 cm^{-1} was attributed to the C-H vibration, the peak at 2834 cm^{-1} was due to symmetric stretching mode of CH_2 and the peak at 2911 cm^{-1} was assigned to the asymmetric stretching mode of CH_2 ³⁶. The appearance of these peaks suggests that CTAB molecules might be present on the surface of ZIF-67. It has been indicated that

introduction of bulky molecules to ZIFs was preferentially via binding to surface of ZIFs rather than penetrating into pores³⁷.

The existence of CTAB can be also revealed by investigating the surface charge of CTAB-ZIF-67 (Fig. 3(a)). Without CTAB, the pristine ZIF-67 already exhibits positive charges under most of pH values. While CTAB was introduced to form CTAB-ZIF-67-L, its zeta potential became slightly more positive. Once more CTAB was added to CTAB-ZIF-67 to form CTAB-ZIF-67-M and CTAB-ZIF-67-H, the surface charges were found to be much more positive. These results validate the existence of CTAB and a higher loading of CTAB can considerably increase the surface charge. Furthermore, we also examined whether the existence of CTAB affected thermal stability of ZIF-67. In the case of the pristine ZIF-67 (Fig. 3(b)), a slight weight loss can first be noticed starting from 100 to 200 °C, possibly owing to the escape of guest molecules such as 2-MIM, methanol and gas molecules from the cavities³⁸. Subsequently, a significant weight loss can be found in the range of 200–300 °C, which was due to the decomposition of the ligand³⁸. When CTAB was added to ZIF-67 to form CTAB-ZIF-67-L, it also started the decomposition starting at 100 °C, followed by a major weight loss occurring from 200 to 300 °C. However, one can notice that the TGA curve in 200-300 °C of CTAB-ZIF-67-L appears slightly different from that of the pristine ZIF-67. To quantitatively compare the TGA curves, T_{50} was used to represent a temperature at which weight loss reaches 50% of its original weight³⁹. For the pristine ZIF-67, its T_{50} is 210 °C, whereas T_{50} of CTAB-ZIF-67-L was 200 °C. Once CTAB loading was further increased in CTAB-ZIF-67 to form CTAB-ZIF-67-M and CTAB-ZIF-67-H, their T_{50} became 195 and 190 °C, respectively. This reveals that the addition of CTAB in fact decreased the thermal stability of ZIF-67 noticeably. One can also observe that the edge of TGA

curve at around 200 °C, where the major weight loss started occurring, shifted to low temperatures, indicating that the decomposition of CTAB-ZIF-67 was initiated at low temperatures. Unlike other polymer-functionalized nanocomposites which can exhibit enhanced thermal stability⁴⁰, the addition of CTAB in fact slightly weakened the thermal stability of ZIF-67 probably because decomposition of alkanes of CTAB occurred at a relatively low temperature. Elemental analyses (*i.e.*, C, N, H) of CTAB-ZIF-67 with different CTAB loadings were also conducted and summarized in Table S2. One can see that CTAB-ZIF-67 contained a higher percentage of carbon and a lower percentage of nitrogen. Since CTAB, although consists of nitrogen, comprises a long alkyl chain, the addition of CTAB in fact led to a higher fraction of carbon and a lower percentage of nitrogen. When a higher loading of CTAB was added to ZIF-67, the carbon fraction in CTAB-ZIF-67 was further increased and the nitrogen fraction was also further decreased, validating that CTAB was introduced into ZIF-67.

Table S3 also shows surface area and porosities of CTAB-ZIF-67 with different CTAB loadings. Surface area of the pristine ZIF-67 is also listed in Table S3 for comparison. When no CTAB was introduced to ZIF-67, the surface area could reach 1710 m² g⁻¹, which agrees with the reported value in the literature⁴¹. However, after the introduction of CTAB to ZIF-67, the surface area and pore volume was found to decrease. The decrease became more significant as more CTAB was loaded in ZIF-67. This result suggests that the introduction of CTAB might deposit on the surface of ZIF-67 as discussed in the IR result, thereby blocking the pores and reducing the surface area.

3.2 Effect of CTAB loading on the adsorption of diclofenac

Adsorption kinetics of diclofenac to CTAB-ZIF-67 with different CTAB loadings can be seen in Fig. 4(a). In order to examine the effect of CTAB loading, we also measured adsorption capacity of the pristine ZIF-67 as a reference. As revealed in Fig. 4(a), while diclofenac adsorption to the pristine ZIF-67 could quickly reach the equilibrium, its q_e was only around 5 mg L^{-1} . Once CTAB was introduced to form CTAB-ZIF-67-L, the q_e is significantly increased to 15 mg g^{-1} . As CTAB loading became even higher in CTAB-ZIF-67-M and CTAB-ZIF-67-H, the q_e was further improved to 38 and 51 mg g^{-1} , respectively, indicating that the addition of CTAB can remarkably enhance the diclofenac adsorption. However, the enhancements in q_e of CTAB-ZIF-67 were not linearly proportional to the CTAB loadings added during the synthesis. Considering that the CTAB loadings in CTAB-ZIF-67-L, CTAB-ZIF-67-M and CTAB-ZIF-67-H were 0.05 g (137 μmol), 0.1 g (274 μmol) and 0.25 g (686 μmol), respectively, we calculated enhancement in q_e (mg g^{-1}) per mole of CTAB added and the result is shown in Fig. 4(b). It can be seen that even though CTAB-ZIF-67-H exhibited the highest q_e , its q_e per mole of CTAB added was not the highest. Instead, CTAB-ZIF-67-M exhibited a higher $q_e/\text{mol-CTAB}$ than other two CTAB-ZIF-67. This reveals that a higher amount of CTAB loading did not guarantee a higher enhancement in q_e . In fact, one can also observe that the CTAB loading was not linearly proportional to the increase in surface charge of ZIF-67 as seen in Fig. 3(a). This suggests that the addition of CTAB was not fully incorporated into ZIF-67 in CTAB-ZIF-67-H and a part of CTAB might be just wasted. Considering that CTAB-ZIF-67-M appeared to be a much efficient CTAB-functionalized ZIF-67, we selected CTAB-ZIF-67-M to investigate other effects on the diclofenac adsorption.

Regardless of the CTAB loading, the result revealed above indicates that the introduction of CTAB remarkably improved the diclofenac adsorption. It has been

revealed that adsorption of organic pollutants to MOFs/ZIFs can occur via the following interactions: electrostatic interactions, Lewis acid-base interactions, hydrogen bonding as well as π - π stacking interactions⁴². Considering that the size of diclofenac seems larger than pores of ZIF-67, the adsorption of diclofenac to ZIF-67 was considered as a surface phenomenon, in which diclofenac might be attracted to the surface-positively-charged CTAB-ZIF-67. As shown in Fig. S3(a), the surface morphology and the post-adsorption XRD pattern of CTAB-ZIF-67 remained almost the same after the diclofenac adsorption (Fig. S3(b)). This suggests that the adsorption of diclofenac to CTAB-ZIF-67 did not considerably alter the morphology and crystalline structure. On the other hand, Fig. S3(c) and (d) reveal IR spectra of diclofenac and CTAB-ZIF-67 before and after the diclofenac adsorption. It can be seen that the post-adsorption IR spectrum did not change significantly, indicating that the diclofenac adsorption did not remarkably change the surface chemical composition of CTAB-ZIF-67. Nevertheless, the spectral features of diclofenac can be observed in the post-adsorption IR spectrum of CTAB-ZIF-67, especially in the range of 1450–1750 cm^{-1} , indicating that diclofenac was indeed adsorbed to the surface of CTAB-ZIF-67. The elemental analyses of CTAB-ZIF-67 after the diclofenac adsorption are also summarized in Table S2. It can be seen that carbon was still the primary constituent in diclofenac. Therefore, the carbon content tended to increase in CTAB-ZIF-67 after the diclofenac adsorption, while the nitrogen content became much smaller. This also suggests that diclofenac was adsorbed to CTAB-ZIF-67.

3.3 Effect of temperature on the adsorption kinetics

The effect of temperature was examined by studying the adsorption kinetics and isotherm at 20, 30 and 40 °C. Fig. 5(a) shows the adsorption kinetics at different

temperatures and the q_t was found to increase considerably at higher temperatures, revealing that elevated temperatures can improve the diclofenac adsorption.

To quantitatively evaluate the effect of temperature on the adsorption, the pseudo first order and the pseudo second rate laws were employed to analyze the adsorption kinetics. The pseudo first rate law can be expressed as follows (Eq.(2)):

$$\ln(q_e - q_t) = \ln q_e - \frac{k_1}{2.303} t \quad (2)$$

where k_1 (min^{-1}) represents the pseudo first order rate constant. Typically, the pseudo first rate law is for examining adsorption behaviors in solid-liquid systems, in which diclofenac is assumed to be adsorbed to single sorption site of CTAB-ZIF-67.

The fitting result using the pseudo first rate law can be represented as the dashed lines in Fig. 5(a), and correlation coefficients (R_f^2) and rate constants, k_f , are listed in Table 1. The k_f value was found to increase at higher temperatures, validating faster kinetics at the elevated temperature. However, the R_f^2 values are all below 0.95, indicating that the pseudo first order rate law was not a satisfactory model to describe the kinetics. Furthermore, the kinetic data were analyzed using the pseudo second order rate law which can be expressed as follows:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e} \quad (3)$$

where k_2 ($\text{g mg}^{-1} \text{min}^{-1}$) is the pseudo second order rate constant. The fitting result is represented by the solid lines in Fig. 5(a). k_2 values (Table 1) are also found to increase at the elevated temperatures and the corresponding correlation coefficients (R_2^2) are all higher than 0.95. In addition, the estimated q_e values of the pseudo second order rate law are also much closer to the experimental q_e (*i.e.*, $q_{e,exp}$) compared to the $q_{e,est}$ obtained by the pseudo first rate law. Thus, the pseudo second order rate law appears to be a relatively satisfactory model to describe the kinetics.

Since the above-mentioned rate laws could not reveal the diffusion mechanism of diclofenac during the adsorption, we additionally employed the Weber-Morris intraparticle diffusion model to analyze the kinetic data. The intraparticle diffusion model, derived from the Fick's second law of diffusion, is typically expressed as follows (Eq. (3))^{43,44}:

$$q_t = k_{P,i}t^{0.5} + C \quad (3)$$

where $k_{P,i}$ denotes the diffusion rate constant at stage i . C is intercept of a plot of $t^{0.5}$ versus q_t , associated with thickness of the boundary layer and also related to the external mass transfer during the adsorption⁴⁴⁻⁴⁶. In general, three sequential stages occur during an adsorption process. In the first stage, adsorbate diffuses from the bulk solution to the external surface of adsorbent. Thus, the first stage is typically referred to “the boundary layer diffusion”⁴⁷. In the second stage, since the remaining concentration of adsorbate decreases, the adsorption process slows down and then approaches to equilibrium state, which is considered as “the third stage”⁴⁸⁻⁵⁰. To focus on the first two stages, plots of q_t versus $t^{0.5}$ for the adsorption of diclofenac are drawn and shown in Fig. S4 (see ESI†). The data points at each temperature can be separated into two groups. The first group of data points represents the first stage and the second one is referred to the second stage. Each group of data points was fitted by the linear regression to examine whether the data points could line up. Table S1 shows that correlation coefficients of the fitting are higher than 0.95, indicating that each group of data points follows the intraparticle diffusion model. However, the regression line of the second stage did not pass through the origin of the plot for all tested temperatures, indicating that the intra-particle diffusion was not the rate-limiting step^{51,52}.

Besides, rate constants at each stage are also summarized in Table S1 and $k_{p,1}$ is much higher than $k_{p,2}$ at each temperature, revealing that the diffusion rate of diclofenac from the bulk phase to the surface of ZIF-67 was much faster than that from the external surface to pores within CTAB-ZIF-67. Besides, we also found that $k_{p,1}$ became larger when the temperature increased, demonstrating the faster mass transfer at elevated temperatures.

3.4 Adsorption isotherm of diclofenac to ZIF-67

Adsorption isotherm of diclofenac to CTAB-ZIF-67 can be seen in Fig. 5(b) and q_e approaches to a higher value at the elevated temperature. To analyze the adsorption isotherm, we first employed the Langmuir isotherm model as follows (Eq.(4)):

$$\frac{C_e}{q_e} = \frac{1}{K_L q_{max}} + \frac{C_e}{q_{max}} \quad (4)$$

where q_{max} represents the maximal adsorption capacity and K_L is the Langmuir adsorption constant which can be related to the adsorption bonding energy. In the Langmuir isotherm model, the adsorption is assumed to occur as a monolayer on a homogenous surface. Since there are limited sites on the surface, the adsorption capacity eventually reaches saturation. The fitting result using the Langmuir isotherm model can be seen as the solid lines in Fig. 5(b). The data points can be properly fitted with correlation coefficients > 0.98 (Table 2) for all tested temperatures, indicating that the adsorption isotherm can be well described by the Langmuir model. Table 2 also lists the maximal adsorption capacities, q_{max} , and the Langmuir adsorption constants, K_L , at different temperatures.

Next, the Freundlich isotherm was employed to model the adsorption isotherm and the Freundlich isotherm can be expressed as follows (Eq. (5)):

$$\ln q_e = \ln K_F + \frac{1}{n} \ln C_e \quad (5)$$

where K_F is the Freundlich constant and $1/n$ represents the heterogeneity factor of adsorbent which is related to the surface heterogeneity of adsorbent. Typically, in the Freundlich isotherm model, both mono-layer and multiple-layer adsorptions are taken into consideration, implying that the physisorption and chemisorption both occur during the adsorption process. The fitting result using the Freundlich isotherm can be represented by the dashed lines in Fig. 5(b) with correlation coefficients listed in Table 2, which are slightly lower than those obtained using the Langmuir model. The Freundlich constant and n are also summarized in Table 2. Considering $n > 1$ at all tested temperatures, an affinity should exist between diclofenac and CTAB-ZIF-67, which might be the electrostatic attraction.

In addition, the Temkin isotherm was also employed to model the adsorption isotherm. In the Temkin isotherm model, the interaction between adsorbate and adsorbent can be expressed by the adsorption energy associated with the surface coverage. Thus, the Temkin isotherm can be expressed in the following equation (Eq. (6)):

$$q_e = \frac{RT}{b} \ln K_T + \frac{RT}{b} \ln C_e \quad (6)$$

where b denotes the Temkin isotherm constant, K_T is the Temkin isotherm equilibrium binding constant, T is the temperature in Kelvin (K) and R is the universal gas constant. Plots of $\ln C_e$ versus q_e of the adsorption isotherm can be seen in Fig. S5(a) (ESI†) and the data points are fitted by the linear regression using the Eq. (6). The data points can be properly fitted by the linear regression, also indicating that a strong affinity exists between diclofenac and CTAB-ZIF-67.

To further investigate whether the adsorption of diclofenac to CTAB-ZIF-67 was associated with the physisorption, we additionally selected the Dubinin-Radushkevich (D-R) isotherm, in which adsorption is in the form of multiple-layer adsorption due to the van der Waals force. Typically, the D-R can be described as follows (Eq.(7)):

$$\ln q_e = \ln q_d - \beta \varepsilon^2 \quad (7)$$

where q_d represents a theoretical isotherm saturation capacity, β denotes the D-R isotherm constant, and ε is Polanyi potential estimated by $\varepsilon = RT \ln (1+1/C_e)$. Fig. S5(b) reveals plots of $\ln q_e$ versus ε^2 . It can be readily found that the data points are not well-represented by the linear fitting and the corresponding correlation coefficients are much lower compared to the afore-mentioned isotherm model.

These modeling results suggest that the adsorption of diclofenac to CTAB-ZIF-67 involved a strong affinity between diclofenac and CTAB-ZIF-67, which could be attributed to the electrostatic attraction between the carboxylic acid of diclofenac and the quaternary amine of CTAB.

3.5 Activation energy and thermodynamic parameters of the diclofenac adsorption to CTAB-ZIF-67

To obtain the activation energy (E_a) of the diclofenac adsorption, the reaction rate constants (*i.e.*, k_2) at various temperatures were used according to the following equation (Eq. (8)):

$$\ln k_2 = \ln k - E_a/RT \quad (8)$$

where k denotes the temperature-independent factor ($\text{g mg}^{-1} \text{min}^{-1}$), R is the universal gas constant and T is the solution temperature in Kelvin. Fig. S6(a) shows the Arrhenius plot based on the Eq.(8) and the slope and intercept can be adopted to determine E_a and k , which are found to be 20.1 kJ mol^{-1} and $0.024 \text{ g mg}^{-1} \text{min}^{-1}$,

respectively (Table 3). Moreover, thermodynamic parameters, such as the free energy (ΔG°) of the adsorption, the enthalpy (ΔH°) and entropy (ΔS°) of the adsorption, can be derived from the Langmuir isotherm constants (*i.e.*, K_L in L mol^{-1}) using the following equations (Eqs.(9) and (10)):

$$\Delta G^\circ = -RT \ln K_L \quad (9)$$

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (10)$$

Table 3 summaries ΔG° values at different temperatures, which are all negative, indicating that the diclofenac adsorption to CTAB-ZIF-67 can occur spontaneously. A plot of ΔG° versus T can be seen in Fig. S6(b). ΔH° and ΔS° of the adsorption can be then determined by the intercept and slope of the linear regression result and listed in Table 3. Considering the positive value of ΔH° , the diclofenac adsorption to CTAB-ZIF-67 was an endothermic as observed in the adsorption kinetics and isotherm. The positive ΔS° also suggests that an affinity existed between diclofenac and CTAB-ZIF-67, which might be the electrostatic attraction as discussed earlier.

3.6 Effects of pH and co-existing ions on the adsorption capacity

Considering that pH of wastewater typically can vary from 4 to 9⁵³, the effect of pH on the diclofenac adsorption was therefore investigated as seen in Fig. 6(a). It can be seen that the q_e remained quite stable in the range of pH = 5–10 and a slight decrease can be noticed when pH changed to 4. The decrease in q_e at pH = 4 might be due to that excess of H^+ in water protonated diclofenac and lessened the electrostatic attraction between diclofenac and CTAB-ZIF-67. However, overall the effect of pH was not significant on the adsorption capacity.

On the other hand, wastewater also contains other compounds which may interfere with the adsorption. To examine the effect of co-existing ions, urine was particularly

selected as a matrix containing diclofenac because the separation of diclofenac from urine has become of great interest recently²⁹. Fig. 6(b) shows the adsorption of diclofenac to CTAB-ZIF-67 from the simulated fresh urine. When $C_0 = 40 \text{ mg L}^{-1}$, around 15 mg L^{-1} of diclofenac was removed at equilibrium. Compared to the removal of diclofenac from DI water (*i.e.*, 25 mg L^{-1}), the adsorption was indeed affected by the complex composition of urine, including salts and urea. Since urine contains a relative high amount of phosphate (*i.e.*, 12 mg L^{-1}), variation of phosphate during the diclofenac adsorption was also shown in Fig. 6(b). It can be found that phosphate was completely removed in the end of the adsorption, showing that a strong competition adsorption occurred between diclofenac and other anions.

3.7 Recyclability and desorption behavior of diclofenac from CTAB-ZIF-67

In this study, recyclability of CTAB-ZIF-67 was also evaluated. Considering that the presence of salts could interfere with the adsorption, the spent CTAB-ZIF-67 was regenerated by washing with a concentrated sodium chloride solution. In order to conveniently regenerate the spent CTAB-ZIF-67, we also employed an acidic ion-exchange (I.E.) resin to desorb diclofenac. The recyclability result can be seen in Fig. 7(a), in which the adsorption capacities of CTAB-ZIF-67 regenerated by the NaCl solution and I.E. resin are 75% and 53%, respectively, of the capacity obtained using the pristine CTAB-ZIF-67, showing that the regeneration was not complete and diclofenac might be still in CTAB-ZIF-67. The difference between the NaCl solution and I.E. resin might be due to that mass concentrations of NaCl and I.E. resin added to solutions were equal but the amount of active sites in the NaCl solution was much more than that in the I.E. resin solution. Since the regeneration using the NaCl solution and I.E. resin only proceeded for 2 hr, we additionally investigated

desorption behavior of diclofenac from CTAB-ZIF-67 using in the presence of NaCl and I.E. resin as shown in Fig. 7(b). When DI water alone was used to regenerate CTAB-ZIF-67, the desorption kinetics was significantly slow even though DI water was also able to desorb diclofenac. Once the I.E. resin was added, the desorption kinetics became significant faster, indicating that the I.E. resin was able to desorb diclofenac from CTAB-ZIF-67. Furthermore, in the presence of NaCl, the desorption kinetics became even faster. The NaCl solution was much more effective than the I.E. resin to regenerate CTAB-ZIF-67 as we observed that the recyclability from the regeneration using the NaCl solution was higher than using the I.E. resin. Despite that the concentrated NaCl was relatively effective to desorb diclofenac, alternative intense methods may be required to regenerate the spent CTAB-ZIF-67, such as elevated temperature and sonication.

Although the XRD pattern of CTAB-ZIF-67 remained almost the same after the diclofenac adsorption, it is still essential to investigate whether Co^{2+} leached out from CTAB-ZIF-67. Fig. S7 shows the release of Co^{2+} from CTAB-ZIF-67 during adsorption. The amount of Co^{2+} released from CTAB-ZIF-67 was found to be only ~ 0.08 wt%, indicating that the Co^{2+} leached out from CTAB-ZIF-67 was insignificant. This also validates that ZIF-67 was highly stable in aqueous environment under the testing condition. Fig. S7 also shows the release of Co^{2+} during the desorption process in the presence of 5 wt% of NaCl and 5 wt% of I.E. resin. It can be seen that even though with 5 wt% of NaCl, the release of Co^{2+} was still around 0.1 wt%, whereas it became 0.05 wt% in the presence of I.E. resin. This suggests that CTAB-ZIF-67 remained intact without significant decomposition during the desorption process.

4. Conclusion

In this study, ZIF-67 was successfully functionalized with CTAB. The resultant CTAB-ZIF-67, regardless of CTAB loading, still can exhibit similar crystallinity and chemical composition to the pristine ZIF-67. CTAB-ZIF-67 was found to exhibit more positive surface charge and therefore enhanced the diclofenac adsorption. Although the presence of CTAB enhanced the diclofenac adsorption up to 10 times, a certain loading of CTAB (0.274 mol-CTAB/mol-Co²⁺) could lead to the most efficient enhancement, probably because over loading of CTAB was not fully incorporated into ZIF-67. The adsorption kinetics and isotherm were also measured and analyzed using rate law and isotherm models. The diclofenac adsorption to CTAB-ZIF-67 was more preferable at the elevated temperatures. The adsorption was also considered to involve with a strong affinity between diclofenac and CTAB-ZIF-67, which might be the electrostatic effect. While the effect of pH was insignificant, the effect of co-existing compounds (*e.g.*, salts) noticeably hindered the adsorption. However, CTAB-ZIF-67 was still able to remove diclofenac from urine. The desorption behaviors of diclofenac from the spent CTAB-ZIF-67 in the presence of NaCl and I.E. resin were also investigated and the concentrated NaCl solution was proven to be a more effective method to regenerate CTAB-ZIF-67, thereby improving its recyclability.

References:

1. J. L. Sotelo, G. Ovejero, A. Rodríguez, S. Álvarez, J. Galán and J. García, *Chem. Eng. J.*, 2014, **240**, 443-453.
2. C.-m. Dai, S.-U. Geissen, Y.-l. Zhang, Y.-j. Zhang and X.-f. Zhou, *Environ. Pollut.*, 2011, **159**, 1660-1666.
3. T. Heberer, *Toxicology Letters*, 2002, **131**, 5-17.
4. S. Mompelat, B. Le Bot and O. Thomas, *Environment International*, 2009, **35**, 803-814.
5. M. Letzel, G. Metzner and T. Letzel, *Environment International*, 2009, **35**, 363-368.
6. S. Webb, T. Ternes, M. Gibert and K. Olejniczak, *Toxicology Letters*, 2003, **142**, 157-167.
7. T. Heberer, *Journal of Hydrology*, 2002, **266**, 175-189.
8. J. Schwaiger, H. Ferling, U. Mallow, H. Wintermayr and R. D. Negele, *Aquatic Toxicology*, 2004, **68**, 141-150.
9. J. L. Oaks, M. Gilbert, M. Z. Virani, R. T. Watson, C. U. Meteyer, B. A. Rideout, H. L. Shivaprasad, S. Ahmed, M. J. Iqbal Chaudhry, M. Arshad, S. Mahmood, A. Ali and A. Ahmed Khan, *Nature*, 2004, **427**, 630-633.
10. J. Hofmann, U. Freier, M. Wecks and S. Hohmann, *Applied Catalysis B: Environmental*, 2007, **70**, 447-451.
11. D. Vogna, R. Marotta, A. Napolitano, R. Andreozzi and M. d'Ischia, *Water Res.*, 2004, **38**, 414-422.
12. F. J. Beltrán, P. Pocostales, P. Alvarez and A. Oropesa, *J Hazard. Mater.*, 2009, **163**, 768-776.
13. S. Kommineni, J. Zoeckler, A. Stocking, S. Liang, A. Flores and M. Kavanaugh, in *Treatment technologies for removal of methyl tertiary butyl ether (MTBE) from drinking water: Air Stripping, Advanced Oxidation Proecess, Granular Activated Carbon, Synthetic Resin Sorbents*, ed. G. Melin, National Water Research Institute, Fountain Valley, Second edn., 2000, ch. 3, pp. 111-208.
14. M. N. Rashed, *Adsorption Technique for the Removal of Organic Pollutants from Water and Wastewater*, 2013.
15. J. W. Yoon, S. H. Jhung, Y. K. Hwang, S. M. Humphrey, P. T. Wood and J. S. Chang, *Adv. Mater.*, 2007, **19**, 1830-1834.
16. J.-R. Li, Y. Ma, M. C. McCarthy, J. Sculley, J. Yu, H.-K. Jeong, P. B. Balbuena and H.-C. Zhou, *Coord. Chem. Rev.*, 2011, **255**, 1791-1823.
17. J.-R. Li, R. J. Kuppler and H.-C. Zhou, *Chem. Soc. Rev.*, 2009, **38**, 1477-1504.

18. N. L. Rosi, J. Eckert, M. Eddaoudi, D. T. Vodak, J. Kim, M. O'Keeffe and O. M. Yaghi, *Science*, 2003, **300**, 1127-1129.
19. P. Horcajada, T. Chalati, C. Serre, B. Gillet, C. Sebrie, T. Baati, J. F. Eubank, D. Heurtaux, P. Clayette, C. Kreuz, J.-S. Chang, Y. K. Hwang, V. Marsaud, P.-N. Bories, L. Cynober, S. Gil, G. Ferey, P. Couvreur and R. Gref, *Nat. Mater.*, 2010, **9**, 172-178.
20. L.-G. Qiu, Z.-Q. Li, Y. Wu, W. Wang, T. Xu and X. Jiang, *Chem. Commun.*, 2008, DOI: 10.1039/B804126A, 3642-3644.
21. K.-Y. A. Lin, H. Yang, C. Petit and F.-K. Hsu, *Chemical Engineering Journal*, 2014, **249**, 293-301.
22. N. A. Khan, B. K. Jung, Z. Hasan and S. H. Jhung, *J Hazard. Mater.*, 2015, **282**, 194-200.
23. B. K. Jung, Z. Hasan and S. H. Jhung, *Chem. Eng. J.*, 2013, **234**, 99-105.
24. K.-Y. A. Lin and H.-A. Chang, *Chemosphere*, 2015, <http://dx.doi.org/10.1016/j.chemosphere.2015.01.041>.
25. K. S. Park, Z. Ni, A. P. Côté, J. Y. Choi, R. Huang, F. J. Uribe-Romo, H. K. Chae, M. O'Keeffe and O. M. Yaghi, *Proceedings of the National Academy of Sciences*, 2006, **103**, 10186-10191.
26. K.-Y. A. Lin and H.-A. Chang, *Water, Air and Soil Pollution* 2015, **In Press**.
27. X.-Z. Kang, Z.-W. Song, Q. Shi and J.-X. Dong, *Asian J. Chem.*, 2013, **25**, 8324-8328.
28. J. Yao, M. He, K. Wang, R. Chen, Z. Zhong and H. Wang, *CrystEngComm*, 2013, **15**, 3601-3606.
29. K. A. Landry and T. H. Boyer, *Water Res.*, 2013, **47**, 6432-6444.
30. A. A. Gouda, M. I. Kotb El-Sayed, A. S. Amin and R. El Sheikh, *Arabian Journal of Chemistry*, 2013, **6**, 145-163.
31. J. Lienert, K. Güdel and B. I. Escher, *Environmental Science & Technology*, 2007, **41**, 4471-4478.
32. S.-H. Hsu, C.-T. Li, H.-T. Chien, R. R. Salunkhe, N. Suzuki, Y. Yamauchi, K.-C. Ho and K. C. W. Wu, *Scientific Reports*, 2014, **4**, 6983.
33. A. F. Gross, E. Sherman and J. J. Vajo, *Dalton Trans.*, 2012, **41**, 5458-5460.
34. M. He, J. Yao, Q. Liu, K. Wang, F. Chen and H. Wang, *Microporous Mesoporous Mater.*, 2014, **184**, 55-60.
35. J. Yao, R. Chen, K. Wang and H. Wang, *Microporous Mesoporous Mater.*, 2013, **165**, 200-204.
36. R. B. Viana, A. B. F. da Silva and A. S. Pimentel, *Advances in Physical Chemistry*, 2012, **2012**, 14.

37. I. B. Vasconcelos, T. G. d. Silva, G. C. G. Militao, T. A. Soares, N. M. Rodrigues, M. O. Rodrigues, N. B. d. Costa, R. O. Freire and S. A. Junior, *RSC Advances*, 2012, **2**, 9437-9442.
38. A. Schejn, L. Balan, V. Falk, L. Aranda, G. Medjahdi and R. Schneider, *CrystEngComm*, 2014, **16**, 4493-4500.
39. N. Wang, Q. Fang, E. Chen, J. Zhang and Y. Shao, *Polymer Engineering & Science*, 2009, **49**, 2459-2466.
40. K.-Y. Andrew Lin, Y. Park, C. Petit and A.-H. A. Park, *RSC Advances*, 2014, **4**, 65195-65204.
41. E.-X. Chen, H. Yang and J. Zhang, *Inorganic Chemistry*, 2014, **53**, 5411-5413.
42. Z. Hasan and S. H. Jhung, *J Hazard. Mater.*, 2015, **283**, 329-339.
43. N. Kannan and M. M. Sundaram, *Dyes and Pigments*, 2001, **51**, 25-40.
44. J. Chen, Y. Cai, M. Clark and Y. Yu, *PLoS ONE*, 2013, **8**, e60243.
45. F.-C. Wu, R.-L. Tseng and R.-S. Juang, *Water Res.*, 2001, **35**, 613-618.
46. I. D. Mall, V. C. Srivastava, N. K. Agarwal and I. M. Mishra, *Chemosphere*, 2005, **61**, 492-501.
47. W. H. Cheung, Y. S. Szeto and G. McKay, *Bioresource Technology*, 2007, **98**, 2897-2904.
48. P. Luo, Y. Zhao, B. Zhang, J. Liu, Y. Yang and J. Liu, *Water Res.*, 2010, **44**, 1489-1497.
49. R. Han, P. Han, Z. Cai, Z. Zhao and M. Tang, *Journal of Environmental Sciences*, 2008, **20**, 1035-1041.
50. X. Yu, G. Zhang, C. Xie, Y. Yu, T. Cheng and Q. Zhou, *BioResources*, 2011, **6**, 936-949.
51. Z. Cheng, X. Liu, M. Han and W. Ma, *J Hazard. Mater.*, 2010, **182**, 408-415.
52. J. Lin, Y. Zhan and Z. Zhu, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2011, **384**, 9-16.
53. T. Zhang, H. Liu and H. H. P. Fang, *Journal of Environmental Management*, 2003, **69**, 149-156.

Table 1 Modeling parameters for the diclofenac adsorption to CTAB-ZIF-67 at different temperatures.

Conditions		Pseudo-first-order			Pseudo-second-order		
Temp. (°C)	$q_{e, \text{exp}}$ (mg g ⁻¹)	k_1 (min ⁻¹)	$q_{e, \text{est}}$ (mg g ⁻¹)	R_1^2	$k_2 \times 10^3$ (g mg ⁻¹ min ⁻¹)	$q_{e, \text{est}}$ (mg g ⁻¹)	R_2^2
20	30	0.14	27.74	0.948	6.53	30.59	0.979
30	38	0.19	35.23	0.921	9.58	37.46	0.961
40	44	0.24	41.07	0.922	11.05	43.90	0.992

Table 2 Model parameters of adsorption isotherm derived from the Langmuir model, the Freundlich model, the Temkin and the Dubinin-Radushkevich at different temperatures.

	Langmuir			Freundlich			Temkin			Dubinin-Radushkevich		
Temp. (°C)	q_{max} (mg g ⁻¹)	K_L (L mg ⁻¹)	R_L^2	K_F (mg g ⁻¹) (L mg ⁻¹) ^{1/n}	n	R_F^2	K_T (J g ⁻¹)	b (J mol ⁻¹)	R_T^2	q_d (mg g ⁻¹)	$K_{ad} \times 10^6$ (mol ² kJ ⁻¹)	R_{DR}^2
20	43.95	0.624	0.993	20.2	3.89	0.992	10.18	308	0.991	37.35	0.22	0.900
30	54.31	0.908	0.987	26.60	3.69	0.983	13.13	243	0.982	46.35	0.13	0.932
40	60.58	1.783	0.986	35.07	3.92	0.982	29.57	230	0.990	52.67	0.052	0.934

Table 3. Activation energy and thermodynamic parameters of the diclofenac adsorption to CTAB-ZIF-67.

E_a (kJ mol ⁻¹)	k (g mg ⁻¹ min ⁻¹)	Temp.	ΔG° (kJ mol ⁻¹)	ΔH° (kJ mol ⁻¹)	ΔS° (kJ mol ⁻¹ K ⁻¹)
		(K)			
20.1	0.024	293	-29.53	40	0.24
		303	-31.5		
		313	-34.29		

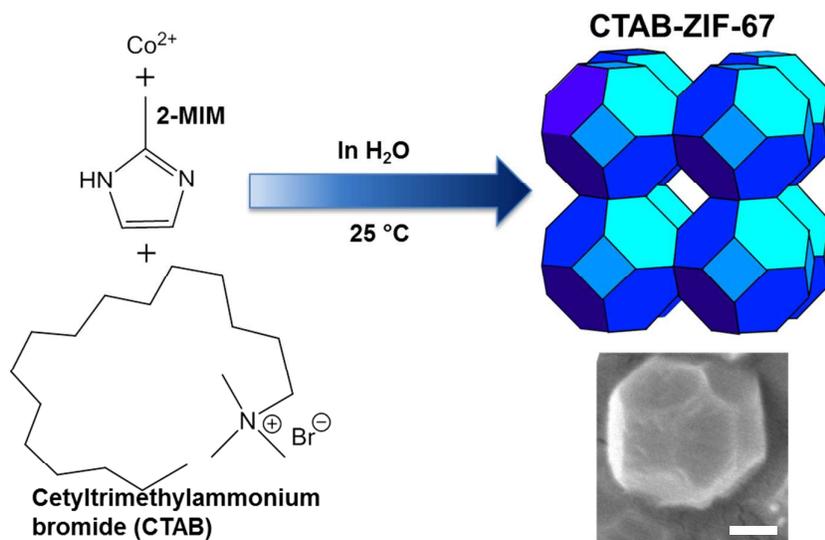


Fig. 1. Schematic illustration of the synthesis of ZIF-67 functionalized with CTAB (scale bar in the SEM image is 200 nm).

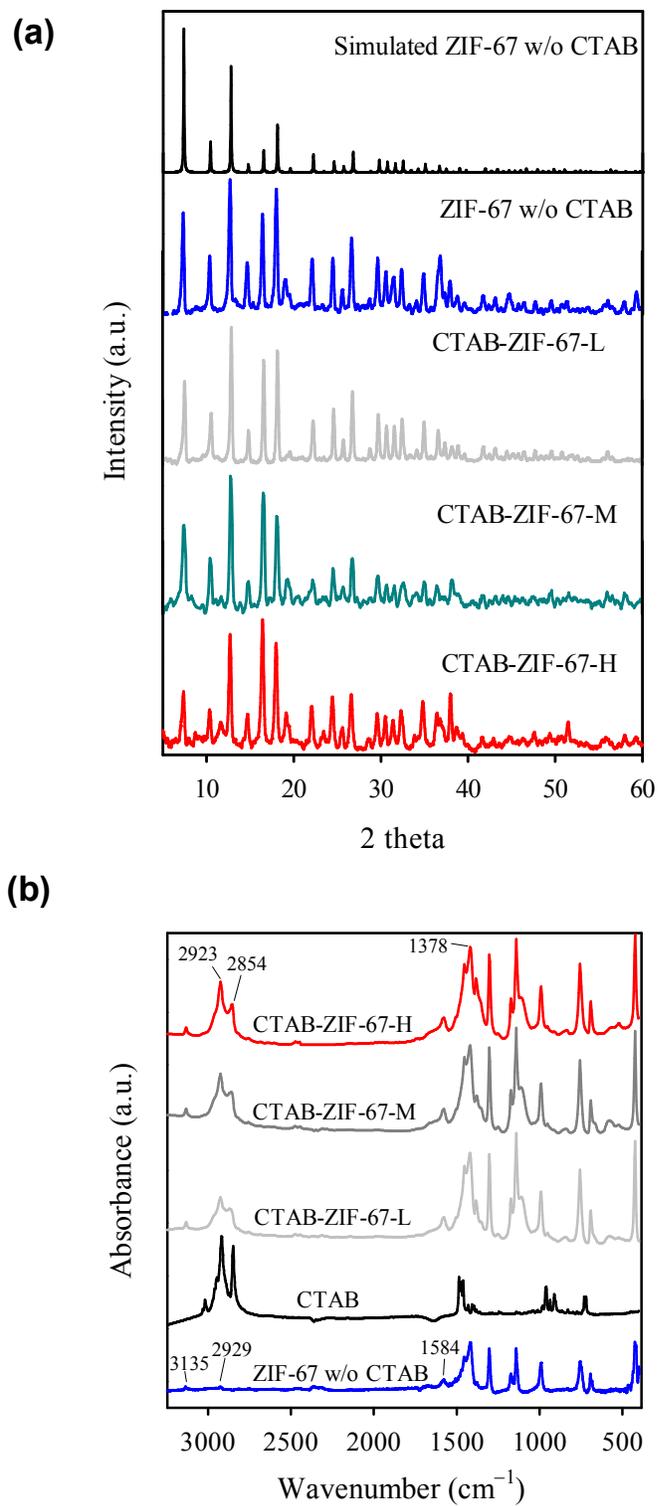


Fig. 2. Characteristics of the pristine ZIF-67 (CTAB-free ZIF-67) and CTAB-ZIF-67:

(a) PXRD patterns and (b) FTIR spectra at ambient temperature

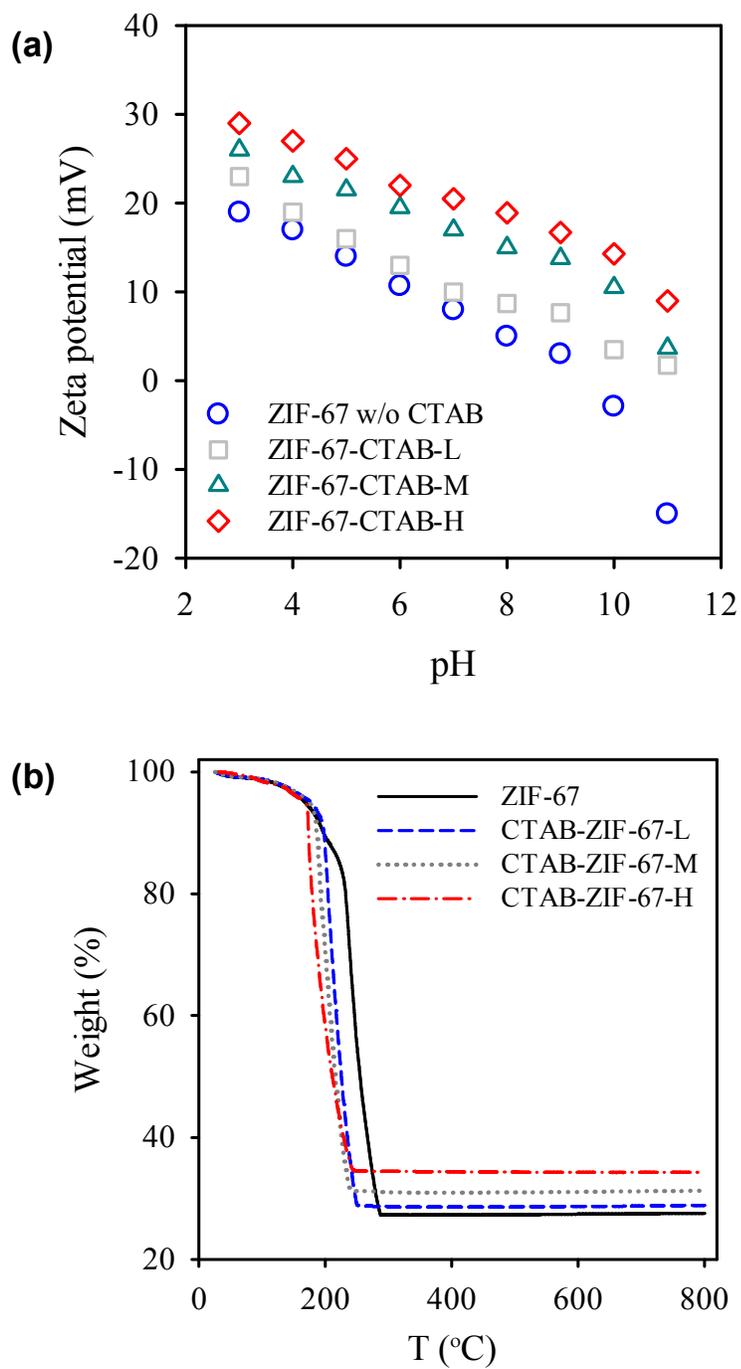


Fig. 3. Effects of CTAB loading on (a) surface charge and (b) thermal stability of CTAB-ZIF-67.

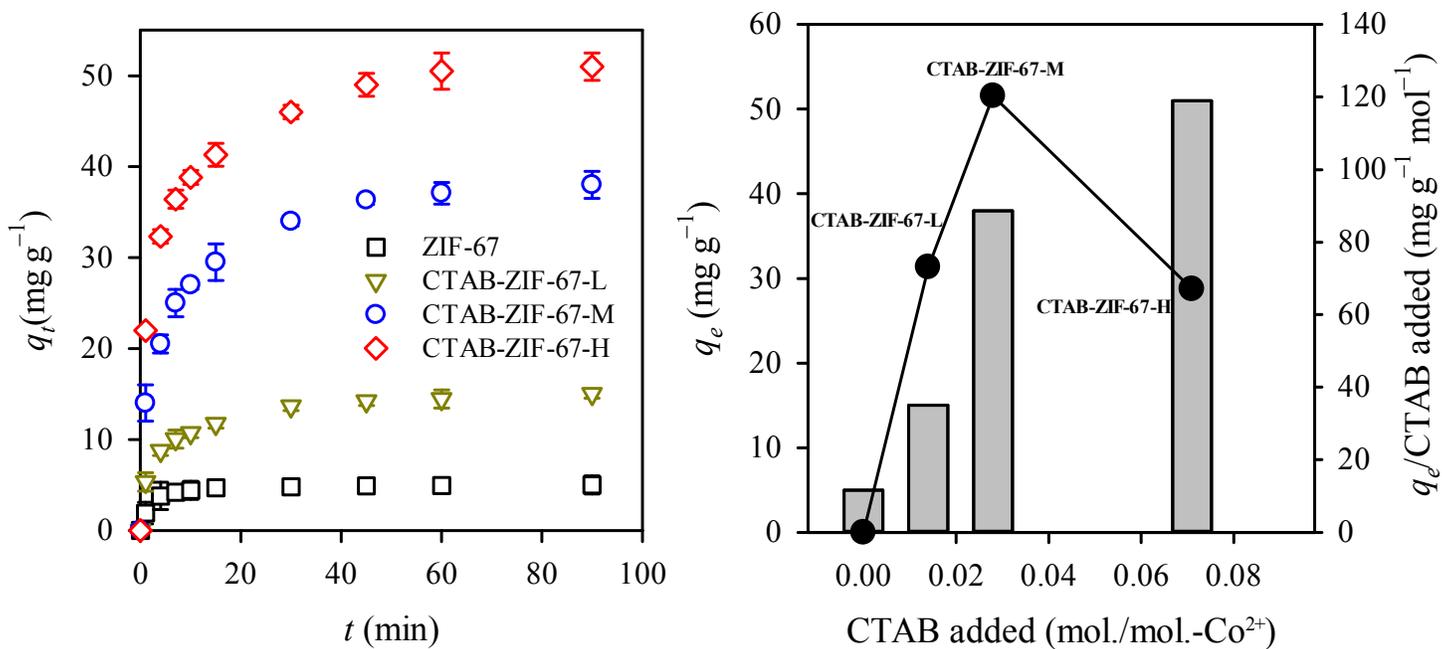


Fig. 4. Effect of CTAB loading on (a) the adsorption kinetics and (b) $q_e/\text{mol-CTAB}$ at 30 °C.

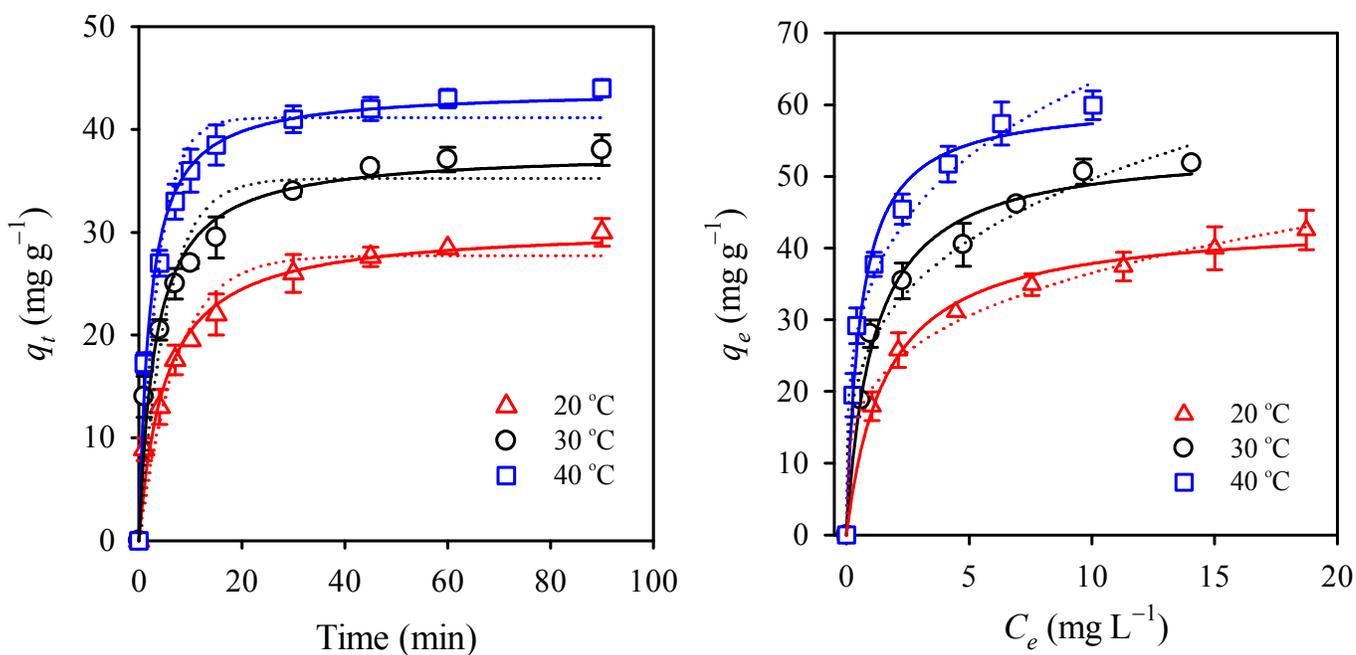


Fig. 5. Effect of temperature on (a) the adsorption kinetics and (b) adsorption isotherm.

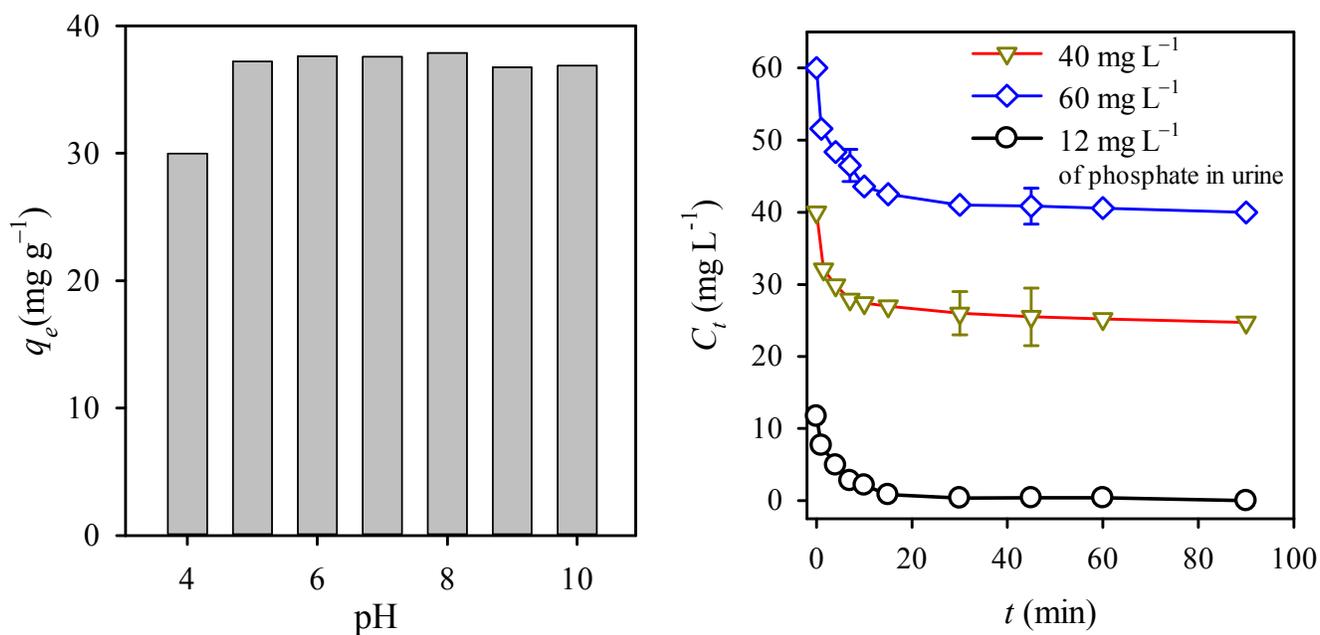


Fig. 6. Effects of (a) pH and (b) co-existing ions from urine on the diclofenac adsorption using CTAB-ZIF-67.

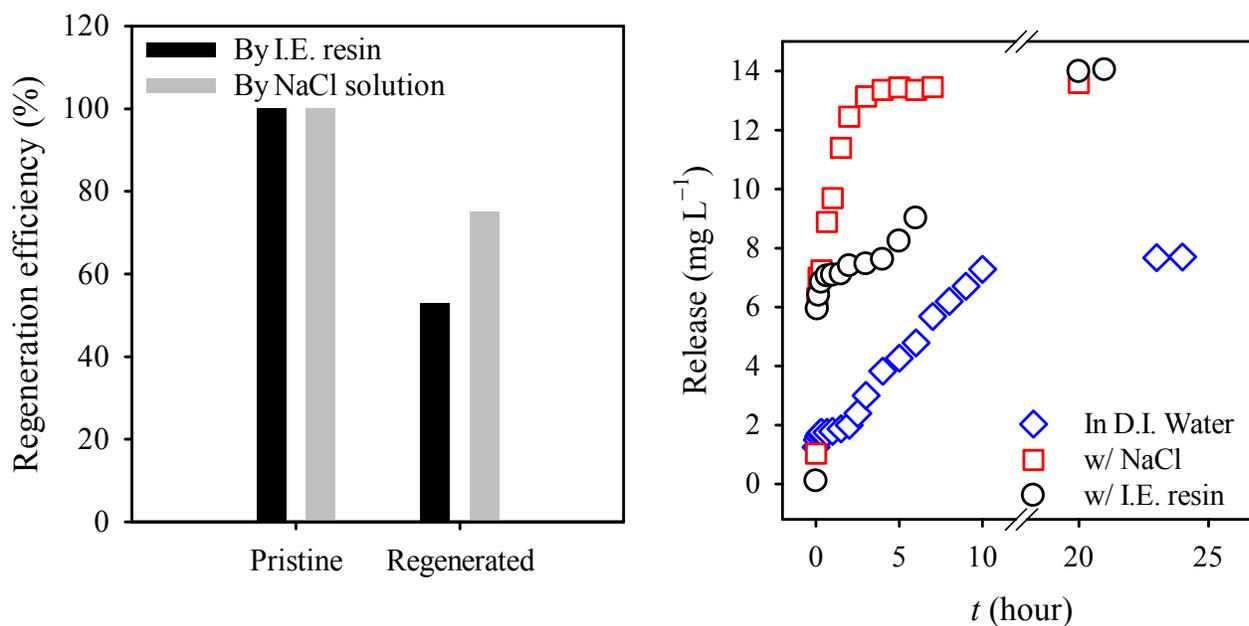


Fig. 7. Effect of regeneration methods on (a) recyclability and (b) desorption behavior of diclofenac from CTAB-ZIF-67 at 30 °C.

