

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

L-Proline-promoted synthesis of 2-amino-4-arylquinoline-3-carbonitriles as sustainable corrosion inhibitors for mild steel in 1M HCl: experimental and computation studies

Chandrabhan Verma^a, M.A. Quraishi^{a*}, L.O. Olasunkanmi^{b, c} and Eno E. Ebenso^{b, c}

^a *Department of Chemistry, Indian Institute of Technology, Banaras Hindu University, Varanasi 221005, India*

^b *Department of Chemistry, North-West University (Mafikeng Campus), Private Bag X2046, Mmabatho 2735, South Africa*

^c *Material Science Innovation & Modelling (MaSIM) Research Focus Area, Faculty of Agriculture, Science and Technology, North-West University (Mafikeng Campus), Private Bag X2046, Mmabatho 2735, South Africa*

***Corresponding author:**

Ph.no. +91-9307025126; Fax: +91- 542- 2368428

E-mail: maquraishi.apc@itbhu.ac.in; maquraishi@rediffmail.com

Abstract:

The inhibition of mild steel corrosion in 1M HCl by 2-amino-4-(4-nitrophenyl) quinoline-3-carbonitrile (AAC-1), 2-amino-4-phenylquinoline-3-carbonitrile (AAC-2) and 2-amino-4-(4-hydroxyphenyl) quinoline-3-carbonitrile (AAC-3) has been investigated using weight loss, electrochemical (potentiodynamic polarization and electrochemical impedance spectroscopy (EIS)), surface (SEM, EDX and AFM) and quantum chemical calculation methods. The results indicated that the investigated inhibitors exhibited good inhibition efficiency against the corrosion of mild steel in acidic solution. The weight loss and electrochemical results

suggested that inhibition efficiencies were enhanced with increase in the concentration of 2-amino-4-arylquinoline-3-carbonitriles (AACs). The results showed that inhibition efficiencies of investigated AACs obeyed the order: AAC-3 (96.52%), AAC-2 (95.65%) and AAC-1 (94.78%). Potentiodynamic polarization study revealed that investigated AACs act as cathodic type inhibitors. Adsorption of the AACs on a mild steel surface obeyed the Langmuir adsorption isotherm. Further, SEM, EDX and AFM studies clearly revealed the film-forming ability of AACs on the mild steel surface. Quantum chemical calculations were undertaken to provide mechanistic insight into the mechanism of inhibition action of AACs. On the basis of experimental and theoretical studies it was concluded that presence of electron releasing hydroxyl (-OH) group in AAC-3 increases inhibition efficiency whereas electron withdrawing nitro (-NO₂) group in AAC-1 decreases the inhibition efficiency.

Keywords: Sustainable, mild steel, electrochemical, SEM/EDX/AFM, Quantum chemical calculations

1. Introduction

Acidic solution is widely used in acid cleaning, acid descaling, oil well acidification and enhanced oil recovery techniques in petroleum and other industries which causes severe economic and safety problems due to corrosion¹⁻³. Among the several available methods, the use of synthetic corrosion inhibitors is the most effective, practical, and economic way to overcome this problem^{4,5}. In this sense, heterocyclic compounds containing polar functional groups (-OH, -NH₂, -CN, -C=C-, -N=N-) and π -electrons in form of double and triple bonds draw much attention due to their high adsorption tendency in addition to their ease and economic synthesis⁶.
⁷. Generally, N-heterocyclic inhibitors adsorb on metallic surface through unshared paired

electrons of heteroatoms (N, O), conjugated double and/ or triple bonds, and aromatic rings^{8,9}. The adsorption of the heterocyclics on metal surface is influenced by several factors such as presence of functional groups, electron density at donor heteroatoms (N, O, and S), and chemical structure^{10,11}. Quinoline and its derivative possess potential applications for synthesis of biologically important compounds such as DNA binding capabilities, antitumor and DNA-intercalating carrier¹². Previously, few reports have been published in which quinoline and its derivatives emphasized as useful metallic corrosion inhibitors¹²⁻¹⁹.

Multicomponent reactions have emerged as a green and powerful technique in synthetic organic chemistry and drug discovery in the sense that several biologically active complex molecules can be synthesized from commercially available cheap starting materials in one step²⁰. Further, the consumption of environmentally benign solvents and chemicals are of particular importance because they contribute many of the green chemistry principles. In asymmetric organocatalysis, use of proline particularly in water and ionic liquids is the most sustainable alternative method as it is directly isolated from natural biological sources without use of any hazardous chemical and solvents such as DMSO, DMF and other chlorinated solvents²¹⁻²³.

The main objective of present work was to compare the corrosion inhibition efficiency of three synthesized 2-amino-4-arylquinoline-3-carbonitriles (AACs) on mild steel corrosion in 1M HCl. Several methods such as weight loss, electrochemical impedance spectroscopy (EIS), scanning electron microscopy (SEM), atomic force microscopy (AFM), and quantum chemical techniques were used for this purpose. The selection criteria of these compounds as corrosion inhibitors was based on the facts that they: (a) can be easily synthesized from commercially available cheap and green starting materials with high yield (b) exhibited excellent inhibition efficiency even at low concentration (c) possess three aromatic rings, several heteroatoms (N, O)

and polar functional groups (-OH -NO₂, -CN, -NH₂) through which they can adsorb on the metal surface (d) have high solubility in testing medium which is attributed due to presence of various polar functional groups.

2. Experimental procedures

2.1. Materials

2.1.1. Synthesis of 2-amino-4-arylquinoline-3-carbonitriles

As described earlier²⁴, the investigated 2-amino-4-arylquinoline-3-carbonitriles (AACs) were synthesized by refluxing a mixture comprising of aniline (1mmol), aldehyde (1 mmol), and malononitrile (1 mmol) and L-proline catalyst (0.05 g, 20 mol %) in water (2 mL) was refluxed for 12 h. The synthetic scheme of the investigated AACs is shown in Fig. 1. Completion of reactions and formation of products were checked by TLC method. After completion of reaction, the reaction mixtures were cooled to room temperature and solid crude products were filtered. The solid crude precipitates were washed with water (10 mL) and finally with ethanol (5 ml) to obtain pure AACs. The synthesized inhibitors were characterized by spectroscopic analysis. The chemical structures, IUPAC name, abbreviation and analytical data of the investigated inhibitors are given in Table 1. The stock solution of inhibitors was prepared in 1M HCl containing 2% acetone.

2.1.2. Electrodes and reagents

For all weight loss and electrochemical experiments, working electrodes were cut from the commercially available mild steel sheet having chemical composition (weight percentage): C (0.076), Mn (0.192), P (0.012), Si (0.026), Cr (0.050), Al (0.023), and Fe (balance). The exposed

surface of the working electrodes were cleaned successively with emery papers of different grade (600, 800, 1000, 1200), washed with deionized water, degreased with acetone, ultrasonically cleaned with ethanol and stored in moisture free desiccator before used in the experiments. Hydrochloric acid (HCl, 37%, MERCK) and double distilled water were used for preparation of test solution (1M HCl).

2.2. Methods

2.2.1. Weight loss measurements

Cleaned, dried and accurately weighted mild steel specimens having dimension $2.5 \times 2.0 \times 0.025 \text{ cm}^3$ were immersed in 1M HCl without and with different concentrations of AACs for 3h. After elapsed time, these specimens were removed, washed with distilled water and acetone, dried in moisture free desiccator, and again weighted accurately. To insure the reproducibility of the weight loss results, each experiment was triply performed and means values were reported at each concentration. From the calculated weight loss, inhibition efficiency ($\eta\%$) was derived using following relationship^{25,26}:

$$\eta\% = \frac{w_o - w_i}{w_o} \times 100 \quad (1)$$

where w_o and w_i are the weight loss values in the absence and presence of AACs at different concentrations, respectively.

2.2.2. Electrochemical measurements

The mild steel specimens with exposed area 1 cm^2 (one sided) were utilized for all electrochemical measurements were performed under potentiodynamic condition using Gamry

Potentiostat/Galvanostat (Model G-300) instrument. Gamry Echem Analyst 5.0 software installed in the computer was used to fit and analyzed the all electrochemical data. The instrument consist of a mild steel working electrode (WE), platinum as a counter electrode and a saturated calomel electrode (SCE) as a reference electrode. Before starting the electrochemical experiments, the working electrode allowed to corrode freely for sufficient time in order to attain steady open circuit potential (OCP). During polarization measurements, the cathodic and anodic Tafel slopes were recorded by changing the electrode potential inevitably from 0.25 to +0.25 V vs. corrosion potential (E_{corr}) at a constant sweep rate of 1.0 mV s⁻¹. The corrosion current density (i_{corr}) was calculated by extrapolating the linear segments of Tafel slopes (cathodic and anodic). From the calculated icorr value inhibition efficiency was calculated using following relation^{25, 26}:

$$\eta\% = \frac{i_{\text{corr}}^0 - i_{\text{corr}}^i}{i_{\text{corr}}^0} \times 100 \quad (2)$$

where, i_{corr}^0 and i_{corr}^i are corrosion current in the absence and presence of AACs, respectively

Electrochemical impedance measurements were carried out at open circuit potential in the frequency range of 100 kHz to 0.01 Hz using AC signal of amplitude 10 mV peak to peak. The charge transfer resistances were calculated from Nyquist plots. The inhibition efficiency was calculated using following equation^{25, 26}:

$$\eta\% = \frac{R_{\text{ct}}^i - R_{\text{ct}}^0}{R_{\text{ct}}^i} \times 100 \quad (3)$$

Where, R_{ct}^0 and R_{ct}^i are charge transfer resistances in absence and presence of AACs, respectively.

2.2.3. SEM, EDX and AFM measurements

For surface analysis, the cleaned mild steel specimens of above mentioned composition were allowed to corrode for 3h in absence and presence of optimum concentration of AACs. Thereafter, the specimens were taken out washed with water, dried and employed for SEM, EDX and AFM analysis. The SEM model Ziess Evo 50 XVP was used to investigate the micromorphology of mild steel surface at 500x magnification. Chemical composition of the inhibited and uninhibited specimens was recorded by an EDX detector coupled to the SEM. NT-MDT multimode AFM, Russia, 111 controlled by solvers canning probe microscope controller was employed for surface analysis by AFM method. The single beam cantilever having resonance frequency in the range of 240–255 kHz in semi contact mode with corresponding spring constant of 11.5N/m with NOVA programme was used for image interpretation. The scanning area during AFM analysis was 5 mm x 5 mm.

2.2.4. *Quantum chemical calculations*

Quantum chemical calculations were carried out on the investigated AACs using the density functional theory (DFT) method involving the Becke three-parameter hybrid functional together with the Lee-Yang-Paar correlation functional (B3LYP)²⁷. The 6-31+G(d, p) basis set was chosen for all the calculations. The calculations were carried out with the aid of Gaussian 09 software for Windows (Revision D.01)²⁸. The optimized geometries of the compounds were confirmed to correspond to their true energy minima by the absence of imaginary frequency in the computed vibrational frequencies. All quantum chemical parameters were derived based on the electronic parameters of the most stable conformers of the molecules. The frontier molecular orbital (FMO) energies, that is, the highest occupied molecular orbital energy (E_{HOMO}) and the lowest unoccupied molecular energy (E_{LUMO}) were calculated. Other parameters such as the energy gap (ΔE), global hardness (η), global electronegativity (χ), and the fraction of electrons

transfer (ΔN) from the inhibitor to the metal atom were computed respectively according to the equations^{29,30}:

$$\Delta E = E_{LUMO} - E_{HOMO} \quad (4)$$

$$\eta = \frac{1}{2}(E_{LUMO} - E_{HOMO}) \quad (5)$$

$$\chi = -\frac{1}{2}(E_{LUMO} + E_{HOMO}) \quad (6)$$

$$\Delta N = \frac{\chi_{Fe} - \chi_{inh}}{2(\eta_{Fe} + \eta_{inh})} \quad (7)$$

where χ_{Fe} and η_{inh} denote the electronegativity and hardness of iron and inhibitor, respectively.

A value of 7 eV/mol was used for the χ_{Fe} , while η_{Fe} was taken as 0 eV/mol for bulk Fe atom in accordance with the Pearson's electronegativity scale³¹. The total energy change (ΔE_T) that accompanies the donor-acceptor charge transfer process was calculated according to the approximation made by Gomez et al.³²:

$$\Delta E_T = \frac{-\eta}{4} \quad (8)$$

where η was approximated to the chemical hardness of the inhibitor molecule. Selected dihedral angles that might have some correlations with the experimental inhibition efficiency of the compounds were also reported.

3. Results and discussion

3.1. Weight loss measurements

3.1.1. Effect of AACs concentration

The weight loss is a reliable, useful, and widely used technique to examine the corrosion inhibition property of inhibitors. The Effect of AACs concentrations on mild steel corrosion at 308 K after 3 immersion time were investigated by weight loss method. Variation of the inhibition efficiency with AACs concentration is shown in Fig. 2 and corrosion parameters such as corrosion rate (C_R), inhibition efficiency ($\eta\%$), and surface coverage (θ) are given in Table 2. From the results it is seen that the values of weight loss (mg) and corrosion rate (C_R) were decreased with an increased in AACs concentration and maximum efficiency was observed at 40 mgL⁻¹ concentration. The AAC-1, AAC-2 and AAC-3 showed maximum efficiency of 94.78%, 95.65% and 96.52%, respectively at 40 mgL⁻¹ concentration and 308 K temperature. The increased AACs concentration causes increased in extent of adsorption and surface coverage due to availability of large number of inhibitor molecules therefore increases inhibition efficiency³³. The difference in the inhibition efficiency might be due to presence of different substituents and molecular size of the AACs³⁴. The AAC-3 attained the highest inhibition efficiency among the studied compounds due to presence of additional electron releasing hydroxyl (-OH) group in the phenyl moiety of aromatic aldehyde in AAC-3. Whereas, AAC-1 exhibited the lowest inhibition efficiency which is attributed due to presence of electron withdrawing nitro (-NO₂) group in the phenyl moiety of aromatic aldehyde.

3.1.2. Kinetic parameters: effect of temperature

Variation of inhibition efficiency ($\eta\%$) and corrosion rate (C_R) with electrolyte solution is given in Table 3. From the result depicted in Table 3 it seen that an increase in electrolyte temperature leads to an increase in the rate of mild steel dissolution and corrosion for inhibited and uninhibited acid solutions. The effect of temperature on metallic dissolution in inhibited solution is highly complex, because at elevated temperature several changes such as rapid

etching, desorption of inhibitor and decomposition and/or rearrangement of inhibitor takes place³⁵. The Arrhenius equation is successfully used to establish the relationship between corrosion rate (C_R) and temperature where the natural logarithm of the corrosion rate (C_R) is a linear function with $1/T$.

$$\log(C_R) = \frac{-E_a}{2.303RT} + \log A \quad (9)$$

where C_R is the corrosion rate in $\text{mg cm}^{-2} \text{h}^{-1}$, A is the Arrhenius pre-exponential factor, R is the gas constant and T is the absolute temperature. The Arrhenius plots (Fig. 3) give a straight line between $\log C_R$ versus $1/T$. The values of activation energy (E_a) for mild steel dissolution were calculated from the slopes ($-\Delta E_a/2.303R$) of the Arrhenius plots and given in Table 4. From the results depicted in Table 4 it is seen that values of apparent activation energies are higher in presence of AACs than in their absence (28.48 kJ mol^{-1}). The higher values of apparent activation energy for AAC-1 (71.40 kJ mol^{-1}), AAC-2 (73.73 kJ mol^{-1}) and AAC-3 (75.65 kJ mol^{-1}) indicated the formation of energy barrier for mild steel dissolution in presence of AACs³⁶. Further, it is assume that electrostatic interaction (physical adsorption) between charged inhibitors and metal surface might cause increase in the values of apparent activation energy in presence of AACs³⁷.

3.1.3. Thermodynamic parameters: Adsorption isotherm

Adsorption nature of inhibitor molecule provides good insight into their inhibition mechanism³⁸. For this purpose several adsorption isotherms including the Langmuir, Temkin, Frumkin and Flory–Huggins isotherms were tested, the best fit was obtained with the Langmuir adsorption isotherm. The Langmuir adsorption isotherm can be best represented as³⁹:

$$K_{ads}C = \frac{\theta}{1-\theta} \quad (10)$$

where K_{ads} is the equilibrium constant of the adsorption process, C is the inhibitor concentration and θ is the surface coverage. The Langmuir isotherm (Fig. 4) gives a straight line between $\log \theta/1-\theta$ versus $\log C$ (molL^{-1}). The values of free energy of adsorption (ΔG_{ads}^0) can be calculated using equation (11). In this equation numerical value of 55.5 represents the molar concentration of water in acid solution:

$$\Delta G_{\text{ads}}^0 = -RT \ln(55.5K_{\text{ads}}) \quad (11)$$

The calculated values of K_{ads} and ΔG_{ads}^0 at each studied temperature in presence of optimum concentration of AACs are given in Table 5. The higher values of K_{ads} in presence of AACs suggest that the AACs adsorbed easily and strongly on the mild steel surface⁴⁰. Inspection of the Table 5 reveals that the values of ΔG_{ads}^0 varied from $-34.62 \text{ kJ mol}^{-1}$ to $-36.96 \text{ kJ mol}^{-1}$, which strongly suggest the physiochemical mode of adsorption by AACs on mild steel surface. Further, the negative sign of ΔG_{ads}^0 validated the spontaneous nature of adsorption by the AACs on mild steel surface⁴¹⁻⁴³.

3.2. Electrochemical measurements

3.2.1. Potentiodynamic polarization studies

Potentiodynamic polarization studied was carried out to understand the mechanism of the mild steel dissolution at anode and evolution of hydrogen at cathode. The current-potential curves for mild steel corrosion without and with several concentrations of three AACs are show in Fig. 5. As reflected from the Tafel slopes, the presence of inhibitors causes significant shift in the anodic and cathodic processes toward lower current relative to the Tafel slopes of blank specimen. And, therefore it is concluded that presence of inhibitors affect the anodic mild steel dissolution as well as the cathodic hydrogen evolution to some extent⁴⁴. Simultaneously, this decrease in anodic and cathodic current densities becomes more significant with increasing

inhibitors concentration. A successful extrapolation of linear segments of the anodic and Tafel cathodic slopes provided some important electrochemical parameters such as corrosion potential (E_{corr}), corrosion current density (i_{corr}), anodic and cathodic Tafel slopes (β_a and β_c), as well as corrosion inhibition efficiency ($\eta\%$). The calculated parameters were listed in Table 6.

From the polarization results depicted in Fig. 5 and Table 6 it is observed that the presence of three inhibitors significantly reduced the values of corrosion current densities without causing any substantial change in the values of E_{corr} . This finding suggests that investigated AACs inhibit mild steel corrosion in acid solution by forming a surface film without changing the mechanism of mild steel corrosion⁴⁵. Further, the shift in E_{corr} values is not very prominent, the maximum shift in E_{corr} values were 59, 65 and 66 mV for AAC-1, AAC-2 and AAC-3, respectively, toward cathodic polarization suggesting that investigated inhibitors acted as mixed type inhibitors mainly cathodic inhibitors⁴⁶.

3.1.2. Electrochemical impedance spectroscopy (EIS) study

The electrochemical impedance spectroscopy is an important technique to study the characteristics and kinetics of electrochemical reactions occurring on the metal surface in acid solution. Nyquist plots for mild steel in absence and presence of different concentration of the inhibitors are given in Fig. 6. The impedance spectrum at each condition gives depressed capacitive imperfect semicircles in high frequency region which is attributed to the charge transfer process and the formation of a protective layer by inhibitors on the metal surface⁴⁷. The imperfect semicircle of the impedance spectrum is attributed to the mass transfer processes, frequency dispersion as well as inhomogeneities and roughness of metal surface⁴⁸. Meanwhile, the diameter of the imperfect semicircles increases on increasing AACs concentrations. This finding suggests that the studied inhibitors strongly aggregate on the mild steel surface and block

the active sites and therefore increases the charge transfer resistance as well as inhibition efficiency^{49, 50}. In the present case, the impedance nature of mild steel corrosion was studied using previously described simple electrical equivalent circuit consisting of a resistor of solution resistance (R_s), a resistor of charge transfer (R_{ct}), and a double layer capacitance⁵¹. The double layer capacitance was replaced by constant phase element (CPE) to find more precise and accurate fit of impedance data. The impedance nature of CPE is defined as follows⁵¹:

$$Z_{\text{CPE}} = \left(\frac{1}{Y_0} \right) [(j\omega)_n]^{-1} \quad (12)$$

Where, Y_0 is the CPE constant, ω is the angular frequency; j is the imaginary number and n is the phase shift (exponent). The values double layer capacitance (C_{dl}) in absence and presence of inhibitors was derived using following relationship⁵²:

$$C_{dl} = Y_0 (\omega_{\max})^{n-1} \quad (13)$$

Where, ω_{\max} is the frequency at which the imaginary part of impedance has attained the maximum (rad s^{-1}) value. Generally, the value of n related to the surface inhomogeneity. The electrochemical behavior of the CPE is related to the value of n . In general, the value of n equal to 0, 1, -1 and 0.5 associated with the resistance, capacitance, inductance and Warburg impedance nature of the metal / electrolyte interface, respectively. In our present work, the value of n varies from 0.777 to 0.998. Upon inspection of the data in Table 7 it can be seen that R_{ct} increased with increase in the AACs concentration while values of C_{dl} decreased with concentration signifying that the AACs functioned by adsorption at the metal/ electrolyte interfaces⁵³. The inhibition efficiency was calculated using equation (6) and maximum observed

efficiencies were 94.27%, 96.08%, and 97.42 for AAC-1, AAC-2 and AAC-3, respectively, at 40 mgL⁻¹ concentration and 308 K temperature.

The Bode plots, shown in Fig. 7a-c exhibited three different segments in absence of AACs. In high frequency region the values of $\log |Z|$ and phase angle (α^0) tend to become zero which is a characteristics response of resistive behavior and corresponds to solution resistance enclosed between reference electrode (saturated calomel electrode) and working electrode (mild steel) ^{54, 55}. However, in the medium frequency region, a linear relationship between $\log |Z|$ against $\log f$, with slope values close to -1 and the phase angle value tends to become -70^0 , were observed. This is a characteristics response of capacitive behavior. An ideal capacitor is associated with slope value of -1 and phase angle value of -90^0 ⁵⁶. The deviation from ideal capacitive behavior in the presence study is attributed due to rough working electrode surface resulted due to corrosion. The careful examination of the Bode plots reveal that the values of phase angle significantly increased and therefore, surface roughness remarkably decreased in presence of AACs due to formation of protective surface film ⁵⁷. Further, Bode plots give one time constant, sigma maxima in the intermediate frequency region. The broadening of this maximum in the Bode plots is attributed due to the adsorption and formation of protective film by inhibitors at the metal/ electrolyte interface ⁵⁸.

3.3. Surface measurements

3.3.1. Scanning electron microscopy (SEM) study

. Fig. 8a reveals a SEM micrograph of mild steel surface before exposing to the test solution which clearly shows the abrading scratches on surface formed during cleaning by SiC

emery papers. The morphology of mild steel specimen surface in Fig.8b reveals that in the absence of AACs, the surface is highly corroded and damaged with some area of localized corrosion which is attributed due to the free acid corrosion of mild steel. However, in the presence of AACs, at their optimum concentration, the surface morphologies (Fig. 8c-e) are remarkably smoothed. By comparing the surface morphology of mild steel in absence and presence of AACs at same magnification (500x), it is seen that in presence of AACs the mild steel surfaces are comparatively less corroded and less damaged. This behavior is because of the formation of protective surface film by AACs. This finding suggests that the AACs inhibit mild steel corrosion in 1M HCl by forming a protecting surface film.

3.3.2. Energy dispersive X-ray (EDX) study

To determine the elements present on the mild steel surface before and after exposure to the AACs solution, the EDX spectra of the specimens were taken after 3h immersion time. Fig.9 represents the EDX spectra of mild steel specimens in absence and presence of AACs at their optimum concentration. In absence of AACs the EDX spectrum shown in Fig.9a gives characteristics peaks of the elements (Fe, Carbon and Oxygen) constituting the mild steel specimen. The presence of low intensity signal corresponding to oxygen (O) is might be due to formation of iron oxide after removal of the specimen from the uninhibited solution during SEM/EDX operation. However, in presence of optimum concentration of AACs (Fig.9b-d), the EDX spectra show additional signals for nitrogen suggesting that in the inhibited solution AACs adsorb on the metal surface and from protective surface film which is responsible for the

appearances of pick for the nitrogen in the EDX spectra of inhibited mild steel specimens. Moreover, the signals corresponding to the oxygen (O) for inhibited mild steel specimens show comparatively high intensities as compare to uninhibited specimens. This finding again suggests the adsorption of AACs on mild steel surface resulting into increased intensity of signals corresponds to the oxygen. The elemental composition of the mild steel surface obtained from EDX analysis is given in Table 8.

3.3.3. Atomic force microscopy (AFM) study

AFM is a powerful tool to study the surface morphology at nano- to micro-scale and has become a new choice to study the influence of inhibitors on the generation and the progress of the corrosion at the metal/solution interface. The 3D AFM micrographs of mild steel specimens after 3h immersion time in absence and presence of AACs at their optimum concentration are shown in Fig. 10. Fig. 10a represents the surface morphology of the mild steel in absence of AACs which reveals a very rough surface. This is concluded that in absence of AACs, the mild steel surface highly corroded resulting in the highly surface roughness. The calculated average surface roughness of the mild steel surface in absence of AACs was 392 nm. However, in presence of AACs (Fig. 10 b-d), the surface morphologies are significantly improved might be due to formation of protective surface film. The protective surface films isolated the specimens from aggressive acid solution and therefore inhibit corrosion. The calculated average surface roughnesses were 194, 139 and 108 nm in presence of inhibitor AAC-1, AAC-2 and AAC-3, respectively.

3.4. Quantum chemical calculations

The optimized structures of the studied compounds showing the dihedral angles between the planes of the atoms labeled a, b, c, d are shown in Fig. 11. It is apparent from Fig. 11 that the phenyl group attached to the 4-position of the quinoline ring is not coplanar with the quinoline ring. Since the structural differences in the three AACs are mainly found on the 4-phenyl group substituent, it may be necessary to compare the degree of planarity/non-planarity of this phenyl group in the three compounds. This is because molecules with high degree of planarity are generally believed to exhibit higher inhibition efficiencies than their corresponding less (non)-planar analogues⁵⁹⁻⁶¹. A flat molecule has the tendency to cover the surface of the metal optimally and also to offer enhanced electrostatic interactions between its coplanar atoms and the metallic atom. The lower inhibition efficiency of AAC-1 despite its more number of N and O atoms compared to the other two compounds could be as a result of the highly electron-withdrawing effect of the nitro group of the 4-nitrophenyl, which reduces the electron density of the aromatic ring, and also the relatively less planarity of the 4-nitrophenyl group compared to AAC-2, which lessens the possible electrostatic interactions between the electron-density of the aromatic group and the charged or polarized metal atom^{62,63}. AAC-3 on the other hand has –OH substituent group at positions 4 making it a potentially better inhibitor than AAC-2 without any substituent. The frontier molecular orbitals provide information about the prospective sites of the molecules involved in donor-acceptor relationship between the inhibitor molecules and the metal atom. The HOMO and LUMO electron density distributions of the studied AACs are shown in Fig. 12. The HOMO electron densities of AAC-1 and AAC-2 are essentially distributed on the atoms in the quinoline ring and extended to the N atom of the amino group attached to the position 2 of the ring. This suggests that the quinoline rings in AAC-1 and AAC-2 play a major role in donating π -electrons to the vacant d-orbital of Fe. There is also the tendency of the 2-

amino group donating σ -electrons to the vacant d-orbital of the Fe. For AAC-3, the HOMO electron densities are distributed over the entire quinoline rings and extended to the 4-hydroxyphenyl and the 2-amino groups. This suggests that the quinoline ring, the 4-hydroxyphenyl and the 2-amino groups are likely to participate in donating electrons to the appropriate vacant orbitals of the Fe for effective corrosion inhibition. The LUMO electron densities in the three compounds are nearly distributed over the entire molecular areas. This suggests that the compounds are capable of accepting electrons from the appropriate occupied orbitals of the Fe atom during the donor-acceptor interactions.

The calculated quantum chemical parameters are listed in Table 9. The E_{HOMO} is a measure of the tendency of a molecule to donate its HOMO electrons to the appropriate vacant orbital of an electron-acceptor during the donor-acceptor interactions. The higher the value of the E_{HOMO} the better will be chance of electron donation by the donor molecule. The results in Table 9 shows that the trend of the E_{HOMO} for the studied compounds is: AAC-3 > AAC-2 > AAC-1, which corresponds to the trend of the observed inhibition efficiency. The E_{LUMO} on the other hand is a measure of the tendency of a molecule to accept electrons into its LUMO from the appropriate occupied orbital of an electron-donor. That is, the lower the value of the E_{LUMO} the better the chance of electron acceptance by the acceptor molecule. The values of the E_{LUMO} obtained for the studied compounds do not correlate with the observed $\eta\%$. The opposite trends of the E_{LUMO} values and the $\eta\%$ suggest that the inhibition potentials of the studied AACs are not informed by their ability to receive electrons from the occupied orbitals of Fe. Similarly, the values of the energy gap (ΔE) and the global hardness (η) often employed as indices of relative reactivity or stability of a molecule do not correlate with the observed $\eta\%$. However, the values of the global electronegativity (χ) show that AAC-3 has the least tendency to hold on to its

electrons or the highest propensity to release its electrons in a favorable donor-acceptor mechanism. The trend of the χ results is in complete agreement with the observed $\eta\%$. The fraction of electrons transferred (ΔN) from an inhibitor molecule to the metal atom can be used as the gauge of the relative performance of a set of inhibitor molecules in electron transfer process. The results in Table 9 show that the trend of ΔN is AAC-3 > AAC-2 > AAC-1, which is in conformity with the trend of the observed $\eta\%$. According to Gomez et al., the change in energy (ΔE_T) that accompanies the electron transfer process from an inhibitor to a metal atom can be used to predict the favorability of the donor-acceptor interactions between the interacting species. A negative value of ΔE_T though does not really predict the occurrence of back-donation; it is an indication that the charge transfer to a molecule, followed by a back-donation from the molecule is energetically favorable. Suppose there is any chance of charge transfer from Fe to the studied inhibitors and also retro-donation from the inhibitor molecules to the Fe, the more negative the value of ΔE_T the better the stabilization of the product of the donor-acceptor relationship. The results in Table 9 suggest that AAC-3 will form a more stable inhibitor-Fe complex compared to the AAC-1 and AAC-2, the trend of ΔE_T values is in agreement with the experimentally observed $\eta\%$.

4. Conclusion

The effect of electron donating hydroxyl (-OH) and electron withdrawing nitro (-NO₂) groups in 2-amino-4-arylquinoline-3-carbonitriles (AACs) was studied on the corrosion behavior of mild steel in 1M HCl. The weight loss and electrochemical results suggest that the inhibition efficiency increases with increasing AACs concentrations. The EIS plots suggest that charge-transfer resistance of the corrosion process increases on increasing AACs concentration due to adsorption of these inhibitors at metal / electrolyte interfaces. The adsorption of the AACs on the

mild steel surface obeyed the Langmuir adsorption isotherm. The values of activation energies suggested that AACs inhibit mild steel corrosion by forming a protective surface film at metal/electrolyte interfaces. The adsorbed layer of the AACs over the surface of mild steel has been furthermore conformed by SEM, EDX and AFM analysis. The experimental results were well supported by quantum chemical calculations.

References:

1. K. Zhang, B. Xu, W. Yang, X. Yin, Y. Liu and Y. Chen, *Corros. Sci.*, 2015, 90, 284–295.
2. S. M. Shaban, I. Aiad, M. M. El-Sukkary, E.A. Soliman and M.Y. El-Awady, *J. Mol. Liq.*, 2015, 203, 20–28.
3. A. A. Farag and T. A. Ali, *J. Ind. Eng. Chem.*, 2015, 21, 627–634.
4. R. Hasanov, S. Bilge, S. Bilgiç, G. Gece and Z. Kılıç, *Corros. Sci.*, 2010, 52, 984–990.
5. C. Verma, P. Singh, I. Bahadur, E.E. Ebenso and M.A. Quraishi, *J. Mol. Liq.* 2015, 209, 767–778.
6. M.A. Amin, Q. Mohsen and O.A. Hazzazi, *Mater. Chem. Phys.*, 2009, 114, 908–914.
7. I.B. Obot, D.D. Macdonald and Z.M. Gasem, *Corros. Sci.*
<http://dx.doi.org/10.1016/j.corsci.2015.01.037>
8. J. Aljourani, K. Raeissi and M. A. Golozar, *Corros. Sci.*, 2009, 51, 1836–1843.
9. M. L. Zheludkevich, K. A. Yasakau and S. K. Poznyak, *Corros. Sci.*, 2005, 47, 3368–3383.
10. F. Bentiss, M. Bouanis and B. Mernari, *J. Appl. Electrochem.*, 2002, 32, 671–678.
11. Q. Qu, S. Jiang and W. Bai, *Electrochim. Acta*, 2007, 52, 6811–6820.
12. E.E. Ebenso and I. B. Obot, L. C. Murulana, *Int. J. Electrochem. Sci.*, 2010, 5, 1574–1586.
13. S. M. Li, H. R. Zhang and J. H. Liu, *Trans. Nonferrous Met. Soc. China*, 2007, 17, 318–325.
14. S. V. Lamaka, M. L. Zheludkevich and K. A. Yasakau, *Electrochim. Acta*, 2007, 52, 7231–7247.

15. G. Achary, H. P. Sachin and Y. A. Naik, *Mater. Chem. Phys.*, 2008, 107, 44–50.
16. A. Popova, M. Christov and A. Vasilev, *Corros. Sci.*, 2011, 53, 1770–1777.
17. M. K. Pavithra, T. V. Venkatesha and K. Vathsala, *Corros. Sci.*, 2010, 52, 3811–3819.
18. X. Wang, H. Yang and F. Wang, *Corros. Sci.*, 2012, 55, 145–152.
19. Eno E. Ebenso, M. M. Kabanda, T. Arslan, M. Saracoglu, F. Kandemirli, L. C. Murulana, Ashish K. Singh, Sudhish K. Shukla, B. Hammouti, K.F. Khaled, M.A. Quraishi, I.B. Obot and N.O. Eddy, *Int. J. Electrochem. Sci.*, 2012, 5643 – 5676.
20. C. Beattie, M. North, P. Villuendas, *Molecules.*, 2011, 16, 3420-3432.
21. N.R. Agrawal, S. P. Bahekar, P. B. Sarode, S. S. Zade and H. S. Chandak, *RSC Adv.*, 2015,5, 47053-47059
22. T. P. Loh, L. C. Feng, H. Y Yang and J. Y. Yang, *Tetrahedron Lett.* 2002, 43, 8741–8743.
23. R. A. Sheldon, *Green Chem.*, 2005, 7, 267-278.
24. A. K. Nezhad, S. Sarikhani, E. S. Shahidzadeh, Farhad Panahi, *Green Chem.*, 2012, 14, 2876–2884.
25. C. B. Verma, M.A. Quraishi and E.E. Ebenso, *Int. J. Electrochem. Sci.*, 2013, 8,7401 – 7413.
26. C.B. Verma, M.J. Reddy and M.A. Quraishi, *Anal. Bioanal. Electrochem.*, 2014, 6, 321-340.
27. A.D. Becke, *J. Chem. Phys.* 1993, 98, 5648–5652.
28. M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, et al. Gaussian 09, Revision D.01; Gaussian, Inc.: Wallingford CT, 2009.

29. S. Martinez, *Mater. Chem. Phys.*, 2003, 77, 97–102.
30. L. O. Olasunkanmi, I. B. Obot, M. M. Kabanda and E. E. Ebenso, *J. Phys. Chem. C*, 2015, 119, 16004–16019.
31. R. G. Pearson, *Inorg. Chem.*, 1988, 27, 734–740.
32. B. Gomez, N. V. Likhanova, M. A. Dominguez, R. Martinez-Palou, A.; Vela and J. L. Gazquez, *J. Phys. Chem. B*, 2006, 110, 8928–8934.
33. M. Yadav, D. Behera, S. Kumar and R. R. Sinha, *Ind. Eng. Chem. Res.*, 2013, 52, 6318–6328.
34. A. Aouniti, K. Khaled and B. Hammouti, *Int. J. Electrochem. Sci.*, 2013, 8, 5925–5943.
35. Li Bai, La-Jun Feng, Hong-Yan Wang, Yong-Bin Lu, Xiao-Wei Lei, Fang-Lin Bai, *RSC Adv.*, 2015, 5, 4716–4726.
36. D. K. Yadav and M. A. Quraishi, *Ind. Eng. Chem. Res.*, 2012, 51, 14966–14979.
37. H. Ashassi-Sorkhabi, B. Shaabani and D. Seifzadeh, *Appl. Surf. Sci.*, 2005, 239, 154–164.
38. N. A. Negm, M. F. Zaki, M. M. Said and S. M. Morsy, *Corros. Sci.*, 2011, 53, 4233–4240.
39. S. Ghareba and S. Omanovic, *Corros. Sci.*, 2010, 52, 2104–2113.
40. Y. Ait Albrimi, A. Ait Addi, J. Douch, R.M. Souto and M. Hamdani, *Corros. Sci.*, 2015, 90, 522–528.
41. R. Yıldız, A. Doner, T. Dogan and I. Dehri, *Corros. Sci.*, 2014, 82, 125–132.
42. R. Yıldız, T. Dogan and I. Dehri, *Corros. Sci.*, 2014, 85, 215–221.
43. X. Li, S. Deng and H. Fu, *Corros. Sci.*, 2011, 53, 302–309.
44. S. K. Saha, A. Dutta, P. Ghosh, D. Sukul and Priyabrata Banerjee, *Phys. Chem. Chem. Phys.*, 2015, 17, 5679–5690.

45. L. C. Murulana, M. M. Kabanda and E. E. Ebenso, *RSC Adv.*, 2015, 5, 28743–28761.
46. H. Z. Alkathlan, M. Khan, M. M. S. Abdullah, A. M. AlMayouf, A. Yacine Badjah-Hadj-Ahmed, Z. A. AlOthman and A. A. Mousa, *RSC Adv.*, 2015, 5, 54283–54292.
47. B. Xu, Y. Ji, X. Zhang, X. Jin, W. Yang, Y. Chen, *RSC Adv.*, 2015, 5, 56049–56059
48. B. D. Mert , A. O. Yüce, G. Kardas and B. Yazıcı, *Corros. Sci.*, 2014, 85, 287–295
49. P. Roy, P. Karfa, U. Adhikari and D. Sukul, *Corros. Sci.*, 2014, 88, 246-253.
50. P. Mourya, S. Banerjee and M. M. Singh, *Corros. Sci.*, 2014, 85, 352-363.
51. C. Verma, P. Singh and M.A. Quraishi, *J. Asso. Arab. Univ. Basic. Appl. Sci.* (2015)
<http://dx.doi.org/10.1016/j.jaubas.2015.04.003>
52. A. Yousefi, S. Javadian, N. Dalir, J. Kakemam and J. Akbari, *RSC Adv.*, 2015, 5, 11697–11713
53. C. B. Verma, M.A. Quraishi and A. Singh, *J. Taiwan Inst. Chem. Eng.*, 2015, 49, 229–239.
54. M. Kissi, M. Bouklah, B. Hammouti and M. Benkaddour, *Appl. Surf. Sci.*, 2006, 252, 4190–4197.
55. E. Naderi, A. H. Jafari, M. Ehteshamzadeha, M. G. Hosseini, *Mater. Chem. Phys.*, 2009, 115, 852-852.
56. H. M. A. El-Lateef, *Corros. Sci.*, 2015, 92, 104–117.
57. J. C. Liu, S.W. Park, S. Nagao, M. Nogi, H. Koga, J. S. Ma, G. Zhang, K. Suganuma, *Corros. Sci.*, 2015, 92, 263–271.
58. M. Behpour, S.M. Ghoreishi, N. Soltani and M. Salavati-Niasari, *Corros. Sci.* 2009, 51, 1073–1082.

59. E. E. Ebenso, M. M. Kabanda, L. C. Murulana, A. K. Singh and S. K. Shukla, *Ind. Eng. Chem. Res.*, 2012, 51, 12940–12958.
60. T. Arslan, F. Kandemirli and E. E. Ebenso, I. Love, H. Alemu, *Corros. Sci.* 2009, 51, 35–47.
61. F. Bentiss and M. Lagrenee, *J. Mater. Environ. Sci.*, 2011, 2, 13–17.
62. C. B. Verma, M.A. Quraishi, Ambrish Singh, , *J. Taiwan Inst. Chem. Eng.*, 2015, [doi:10.1016/j.jtice.2015.06.020](https://doi.org/10.1016/j.jtice.2015.06.020)
63. C. Verma, A. Singh, G. Pallikonda, M. Chakravarty, M.A. Quraishi, I. Bahadur, E.E. Ebenso, *J. Mol. Liq.*, 2015, 209, 306–319.

Figure Caption

Fig.1: Synthetic rout of studied AACs

Fig.2: Variation of inhibition efficiency with AACs concentration

Fig. 3: Arrhenius plots for the corrosion rate of mild steel versus the temperature in 1M HCl

Fig.4: Langmuir isotherm plots for the adsorption of AACs on mild steel surface in 1M HCl

Fig. 5 a-c: Polarization curves for mild in absence and presence of different concentration of AACs

Fig.6. a-c: Nyquist plot for mild steel in 1 M HCl without and with different concentrations of AACs

Fig. 7 a-c: Bode ($\log f$ vs $\log |Z|$) and phase angle ($\log f$ vs α_0) plots for mild steel in 1 M HCl in absence and presence of different concentration of AACs.

Fig.8 (a-e): SEM images of mild steel surfaces: (a) abraded, (b) in absence of AACs and in the presence of 40 mgL^{-1} of (c) AAC-1, (d) AAC-2, and (e) AAC-3

Fig.9 (a-d): EDX images of mild steel: (a) in absence of AACs and in the presence of 40 mgL^{-1} of (b) AAC-1, (c) AAC-2, and (d) AAC-3

Fig.10 (a-d): AFM images of mild steel: (a) in absence of AACs and in the presence of 40 mgL^{-1} of (b) AAC-1, (c) AAC-2, and (d) AAC-3

Fig. 11: Optimized molecular structures of the studied compounds showing the dihedral angles a-b-c-d (in degrees).

Fig. 12: The frontier molecular orbital of studied AACs (a) AAC-1 (left, HOMO; right, LUMO), (b) AAC-2 (left, HOMO; right, LUMO) and (c) AAC-3 (left, HOMO; right, LUMO)

Table Caption

Table 1. IUPAC name, molecular structure, molecular formula, melting point and analytical data of studied AACs

Table 2: The weight loss parameters obtained for mild steel in 1 M HCl containing different concentrations of AACs

Table 3: Variation of C_R and $\eta\%$ with temperature in absence and presence of optimum concentration of AACs in 1M HCl

Table 4: Values of activation energies for mild steel dissolution in 1M HCl in the absence and at of optimum concentration of AACs

Table 5: The values of K_{ads} and ΔG_{ads}° for mild steel in absence and presence of optimum concentration of AACs in 1M HCl at different studied temperature

Table 6: Tafel polarization parameters for mild steel in 1 M HCl solution in absence and at different concentration of AACs

Table 7: EIS parameters obtained for mild steel in 1 M HCl in absence and presence of different concentration of AACs

Table 8: Elemental composition of mild steel surface in absence and presence of optimum concentration of AACs after 3h immersion time

Table 9: Quantum chemical parameters derived from the B3LYP/6-31+G(d,p) method

Figure

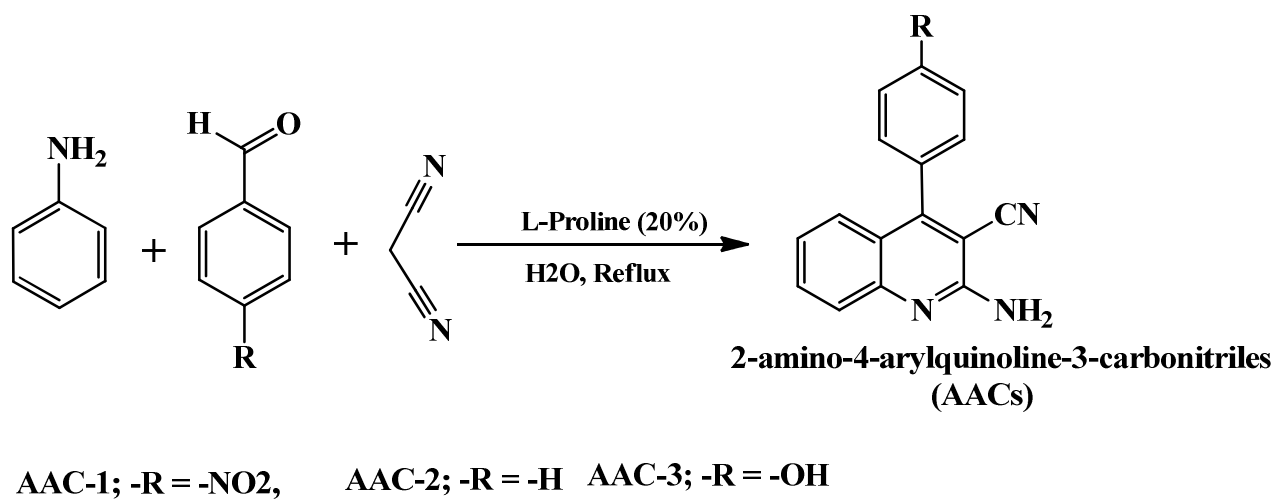


Fig.1: Synthetic rout of studied AACs

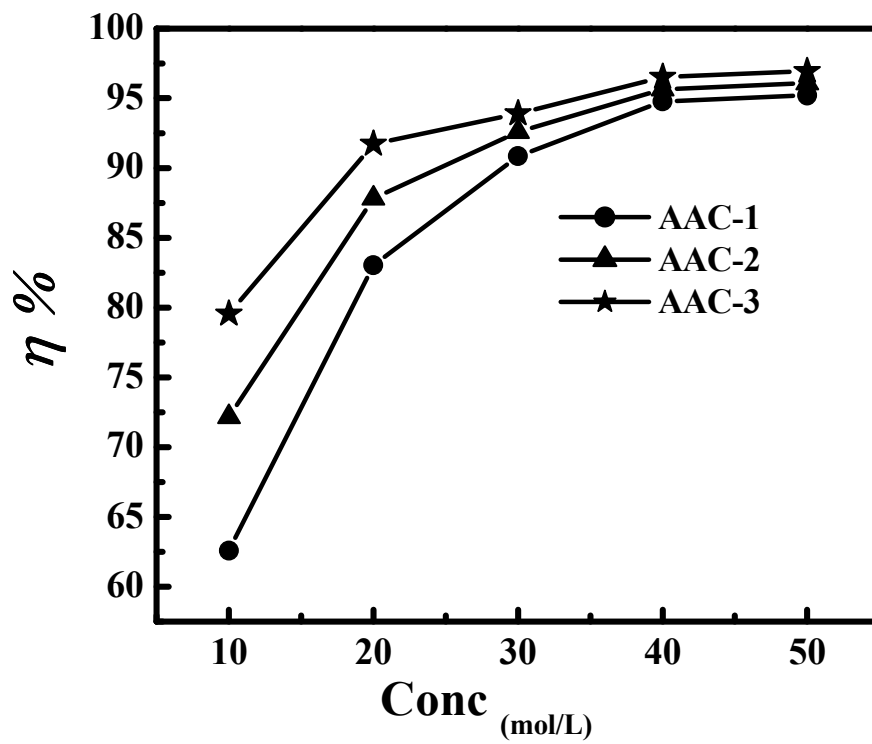


Fig.2: Variation of inhibition efficiency with AACs concentration

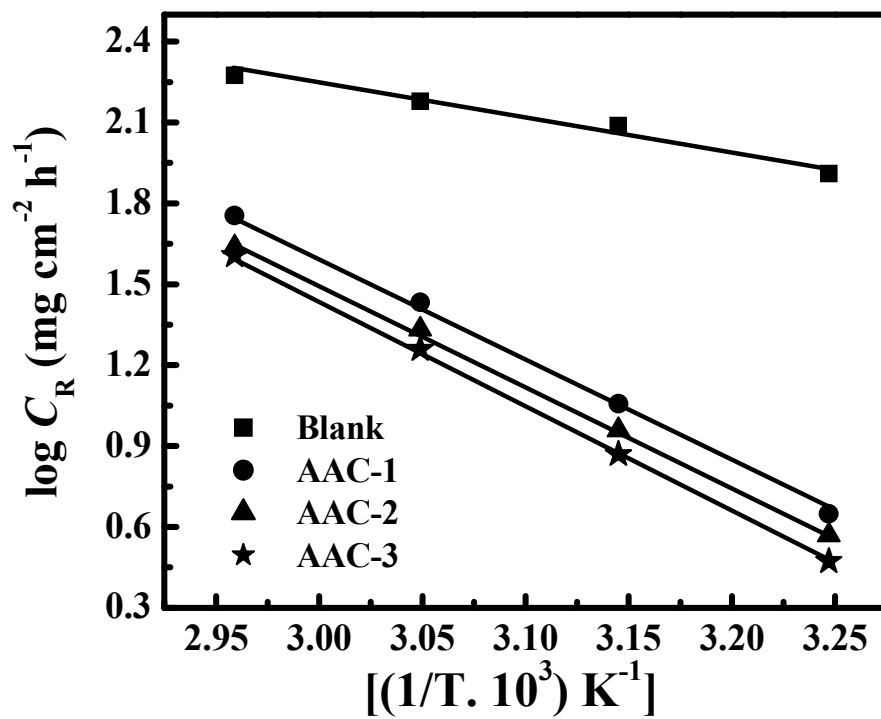


Fig. 3: Arrhenius plots for the corrosion rate of mild steel versus the temperature in 1M HCl

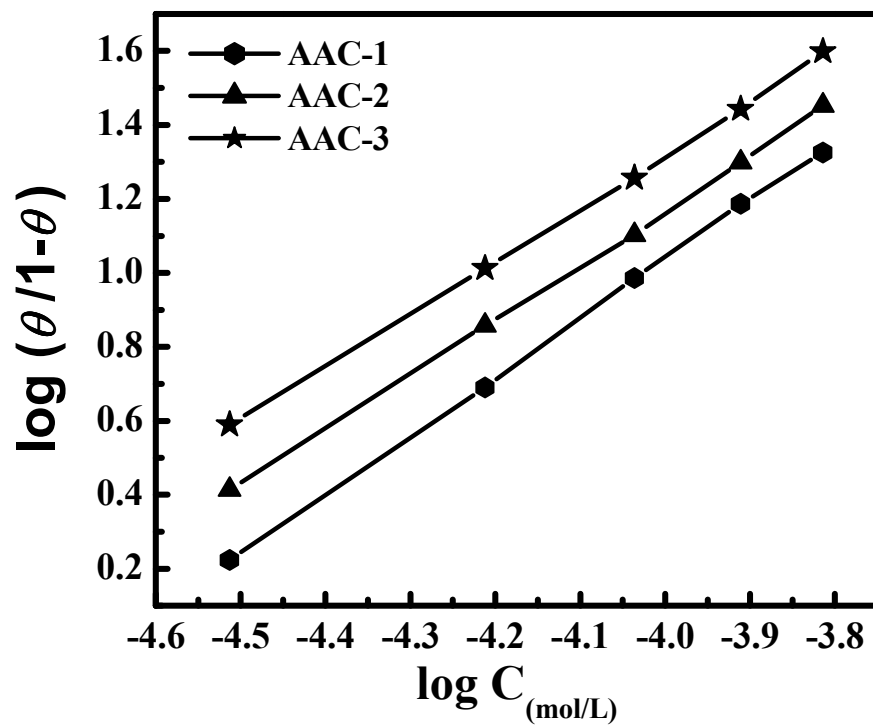


Fig.4: Langmuir isotherm plots for the adsorption of AACs on mild steel surface in 1M HCl

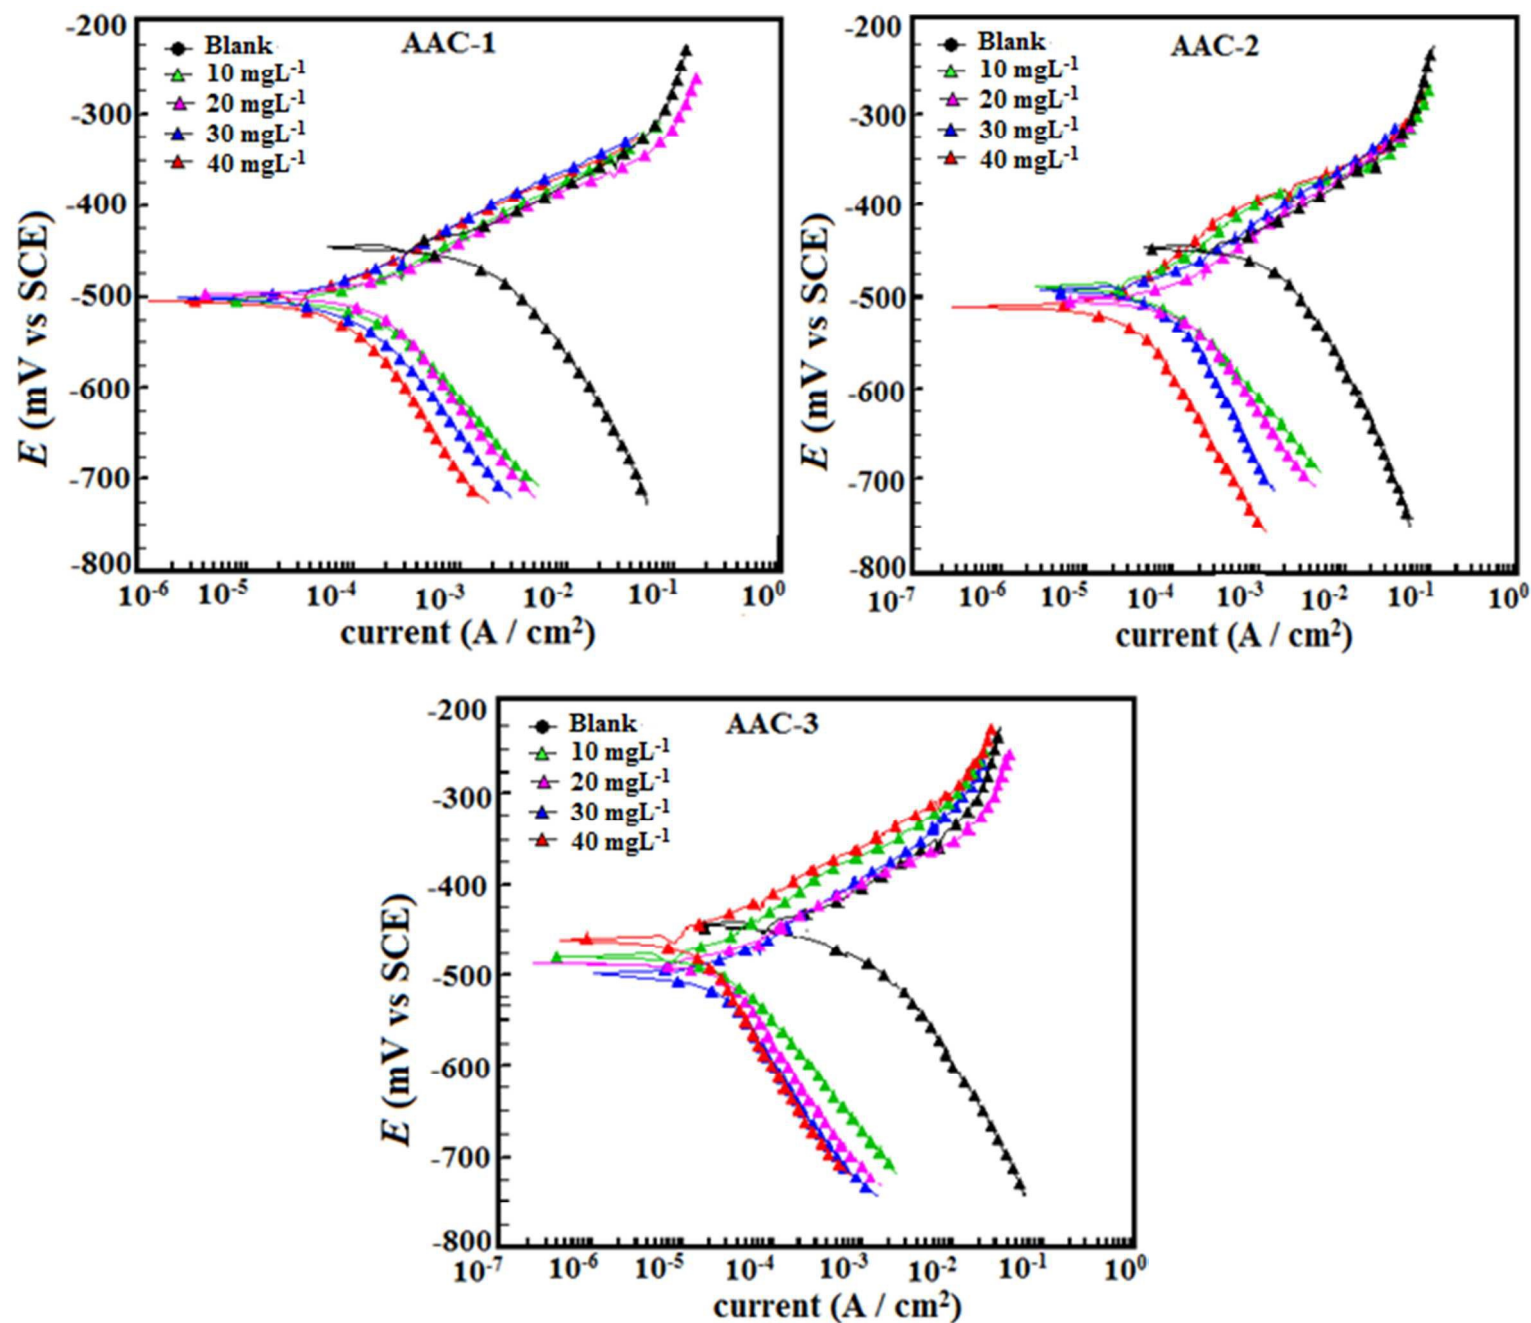


Fig. 5 a-c: Polarization curves for mild in absence and presence of different concentration of AACs

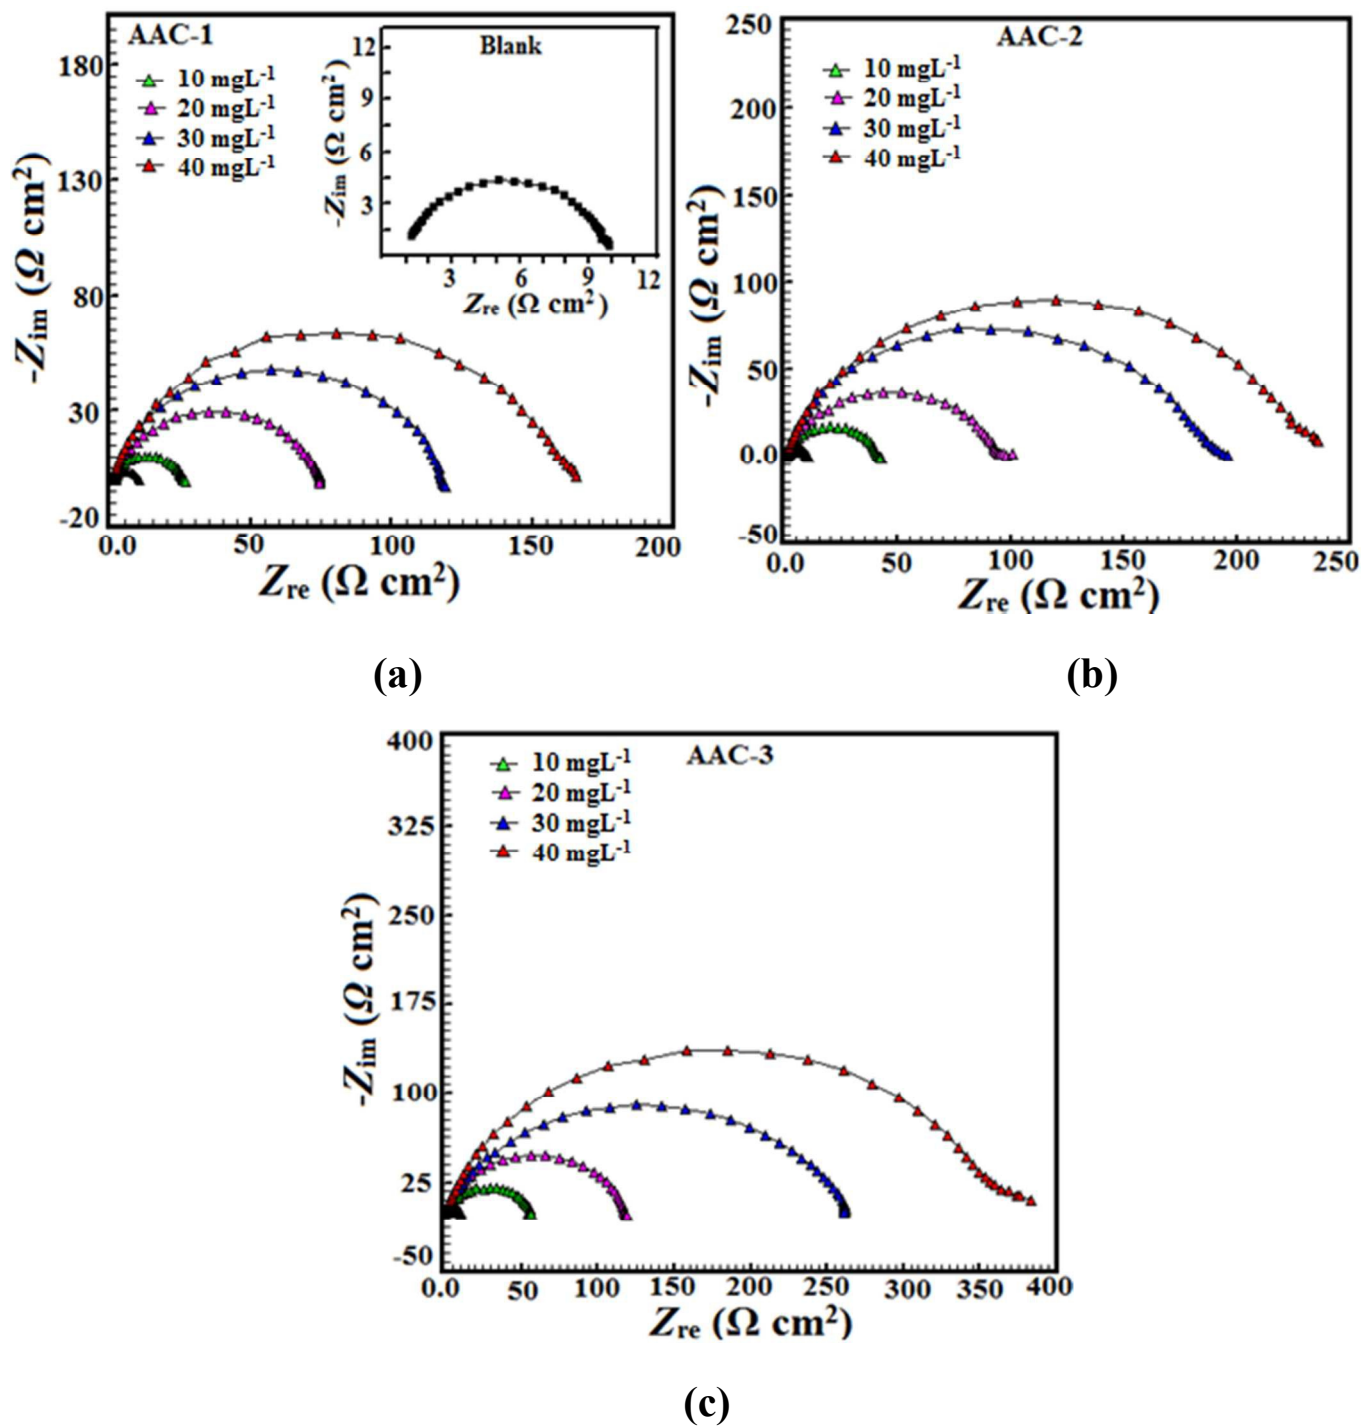


Fig. 6. a-c: Nyquist plot for mild steel in 1 M HCl without and with different concentrations of AACs

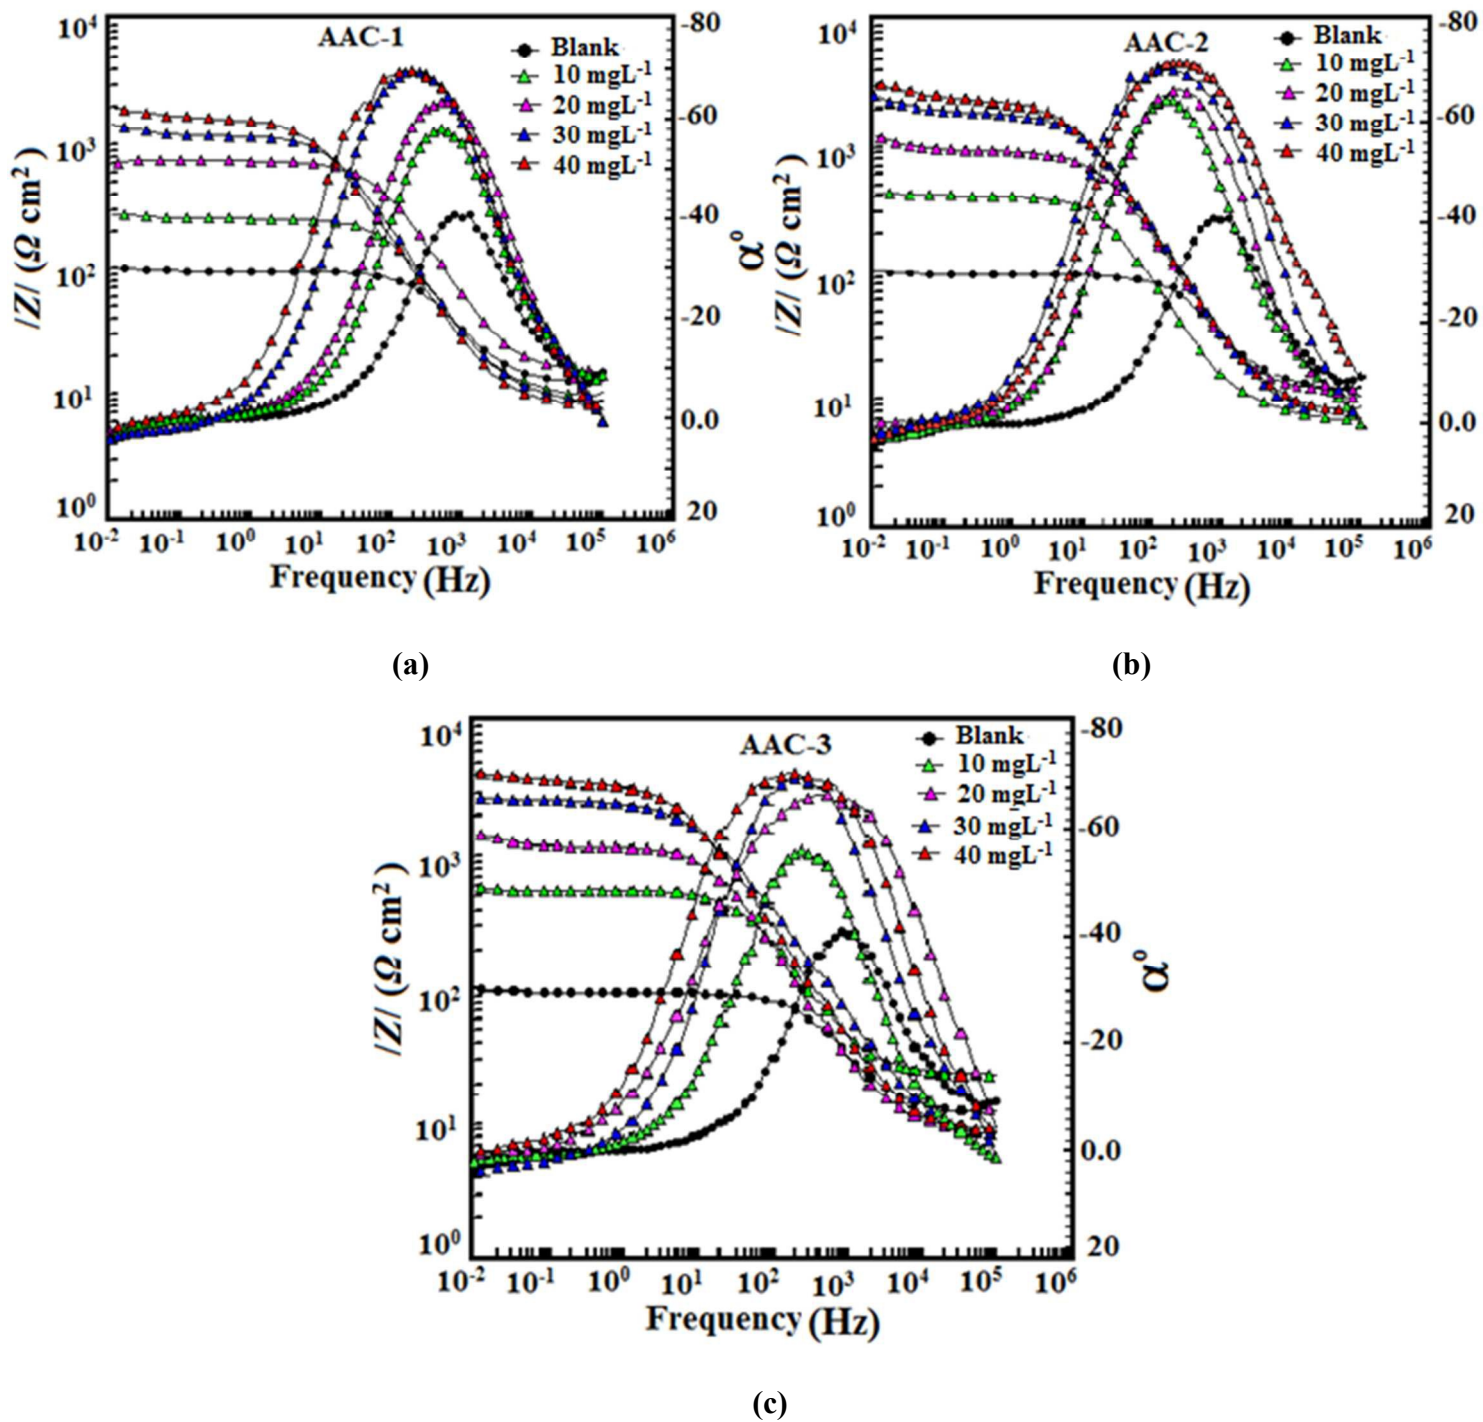
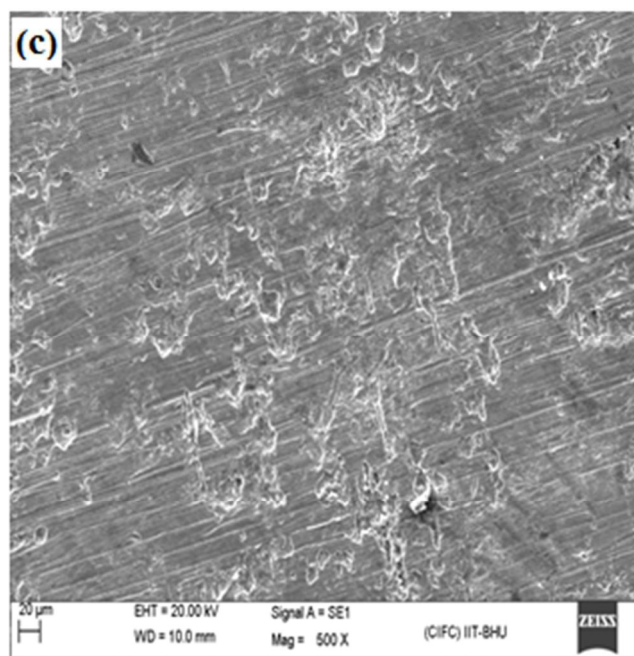
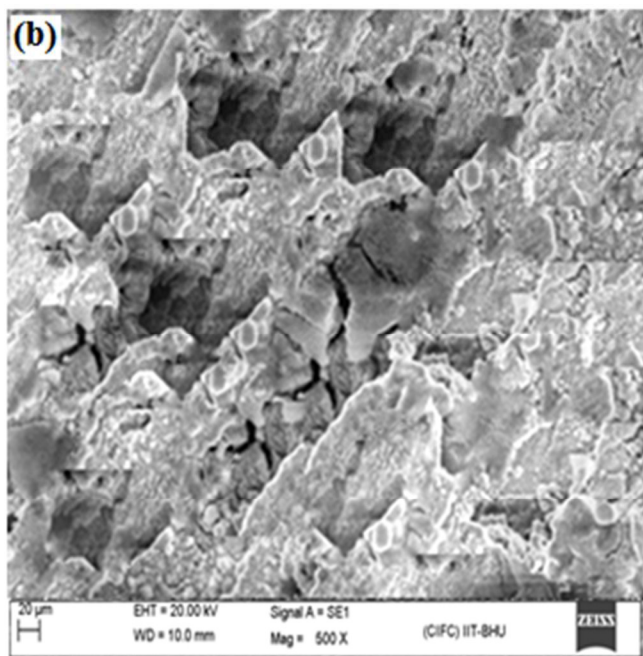
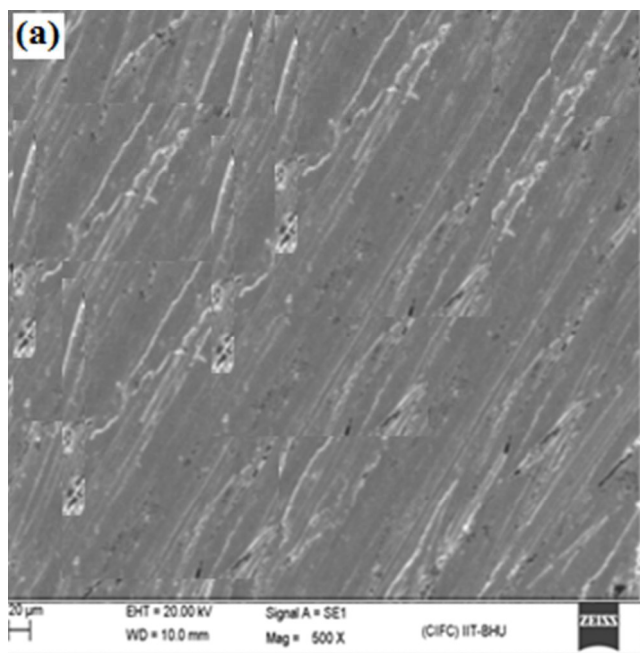


Fig. 7 a-c: Bode ($\log f$ vs $\log |Z|$) and phase angle ($\log f$ vs α°) plots for mild steel in 1 M HCl in absence and presence of different concentration of AACs.



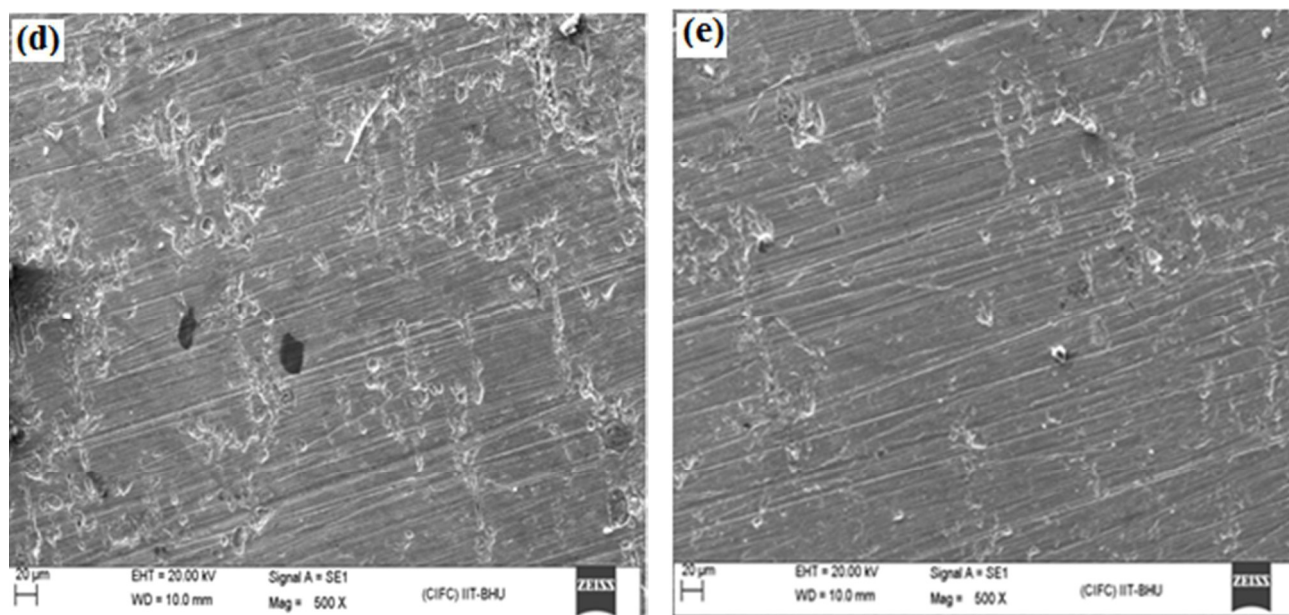
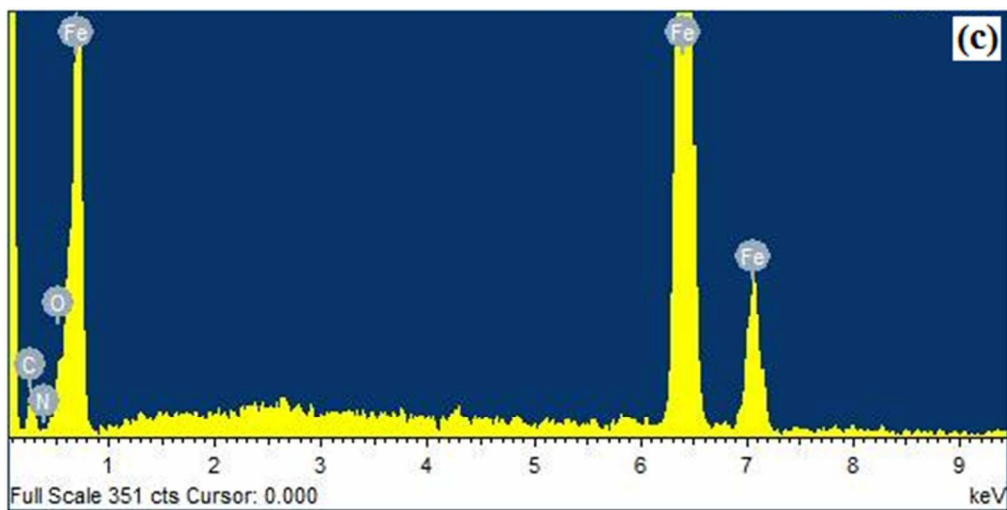
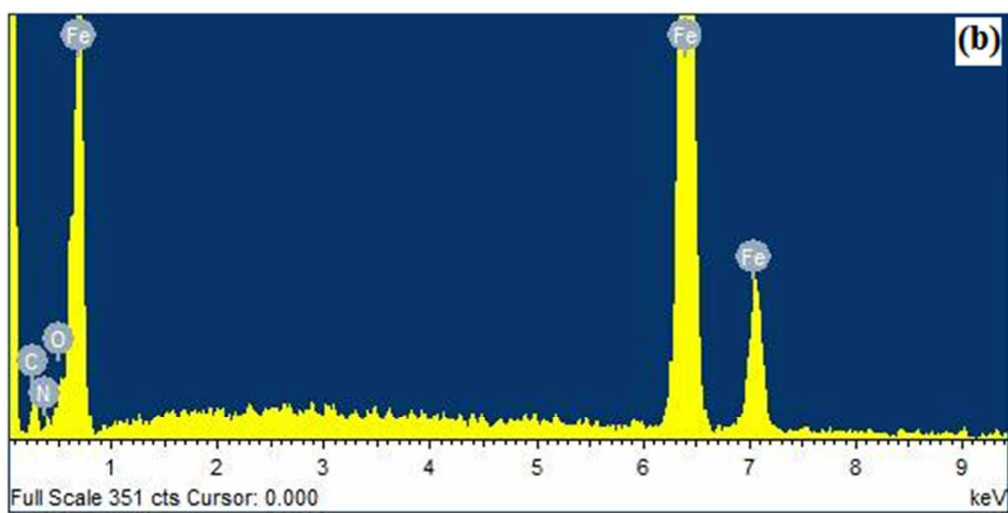
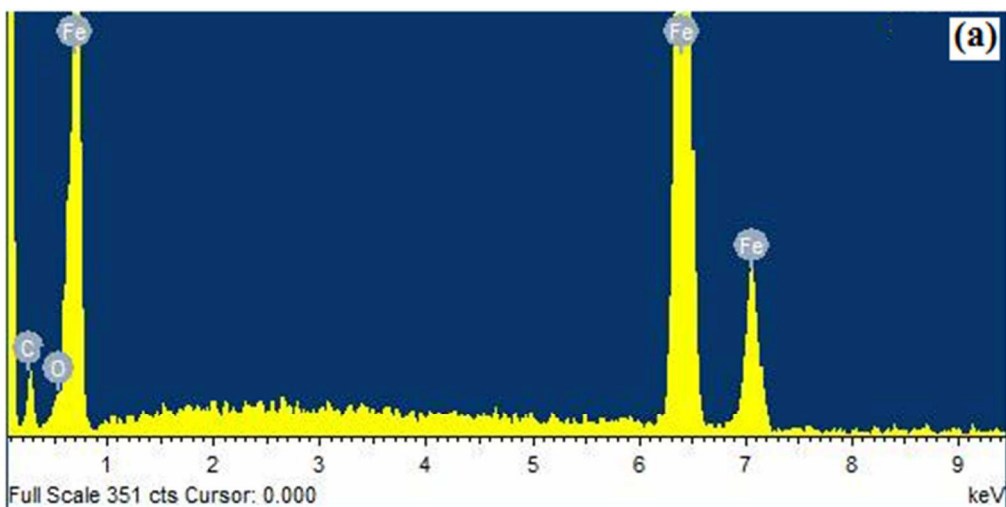


Fig.8 (a-e): SEM images of mild steel surfaces: abraded (a), in absence of AACs (b) in the presence of 40 mgL^{-1} of AAC-1(c), AAC-2(d), and AAC-3(e)



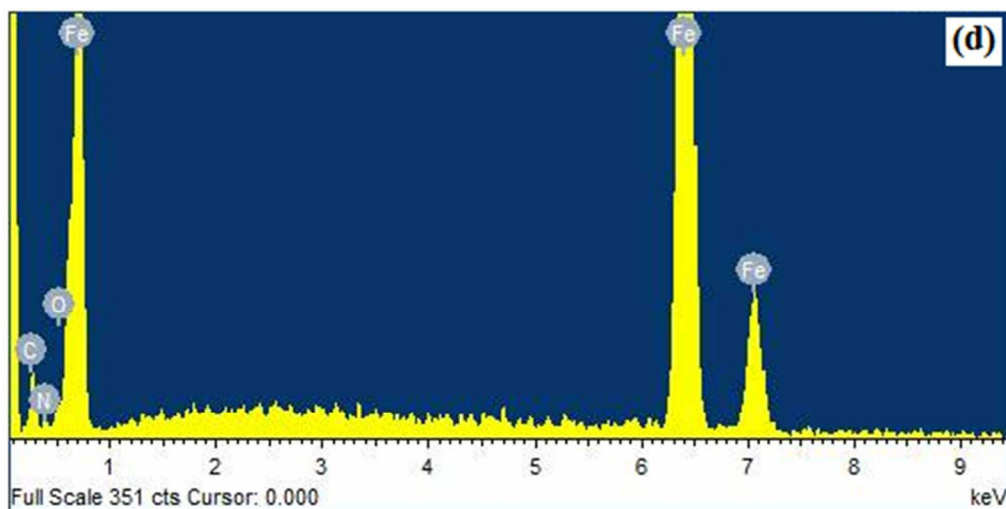
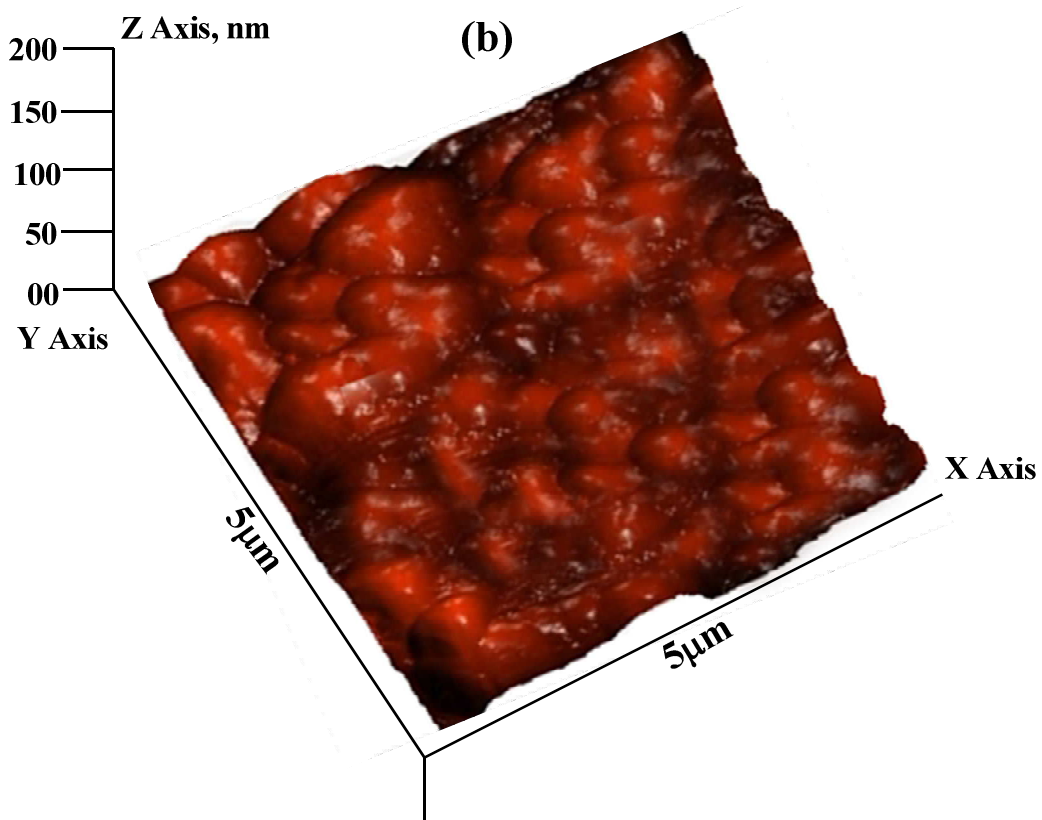
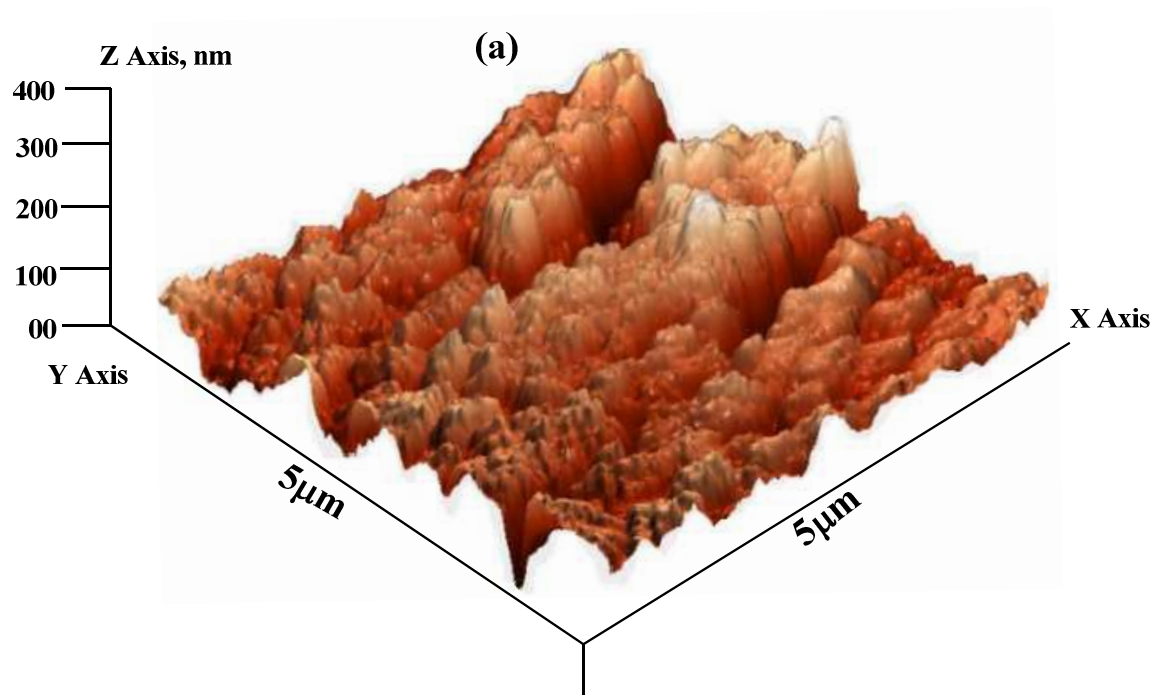


Fig.9 (a-d): EDX images of mild steel: (a) in absence of AACs and in the presence of 40 mgL^{-1} of
(b) AAC-1, (c) AAC-2, and (d) AAC-3



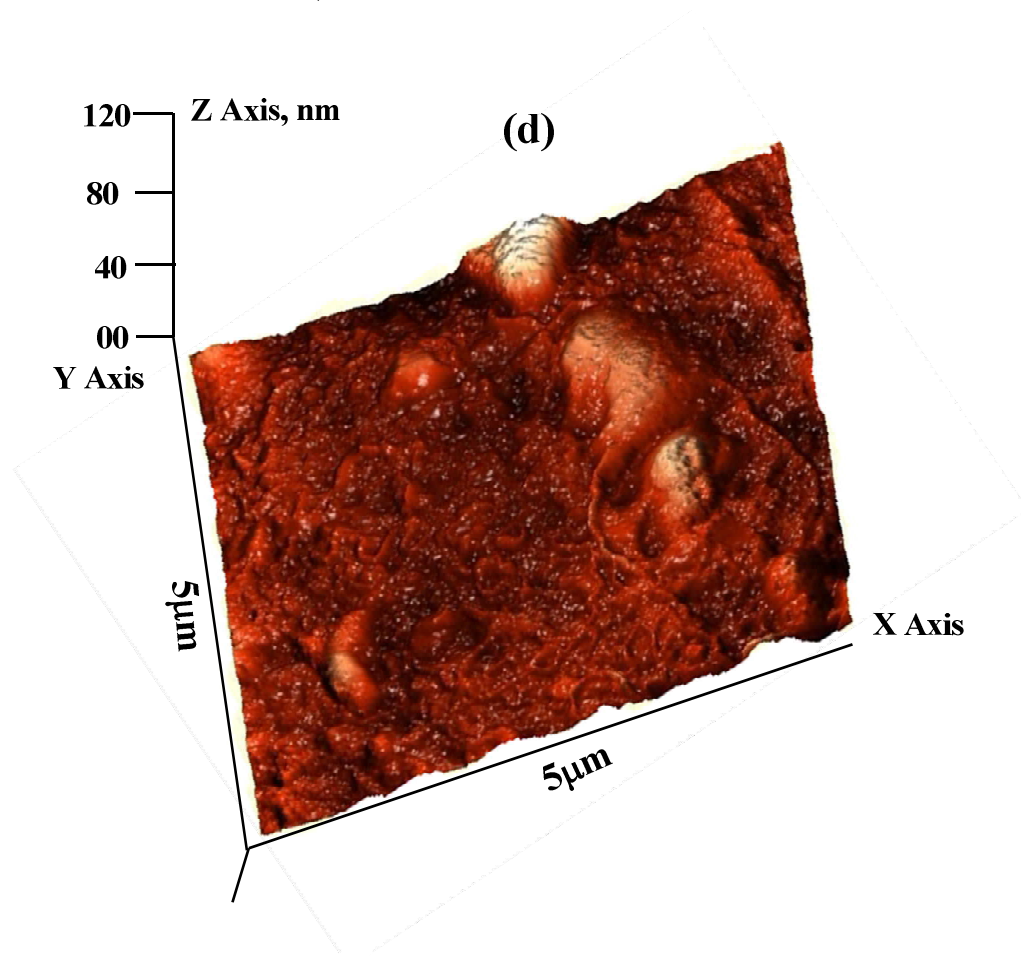
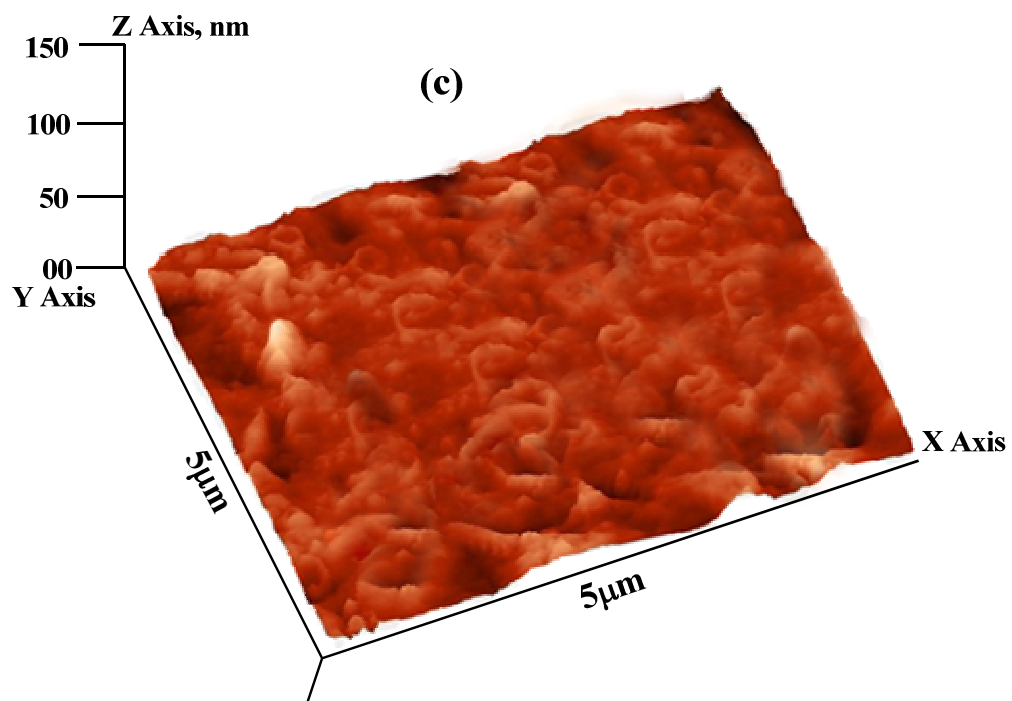


Fig.10. AFM images of mild steel: (a) in absence of AACs and in the presence of 40 mgL^{-1} of (b) AAC-1, (c) AAC-2, and (d) AAC-3

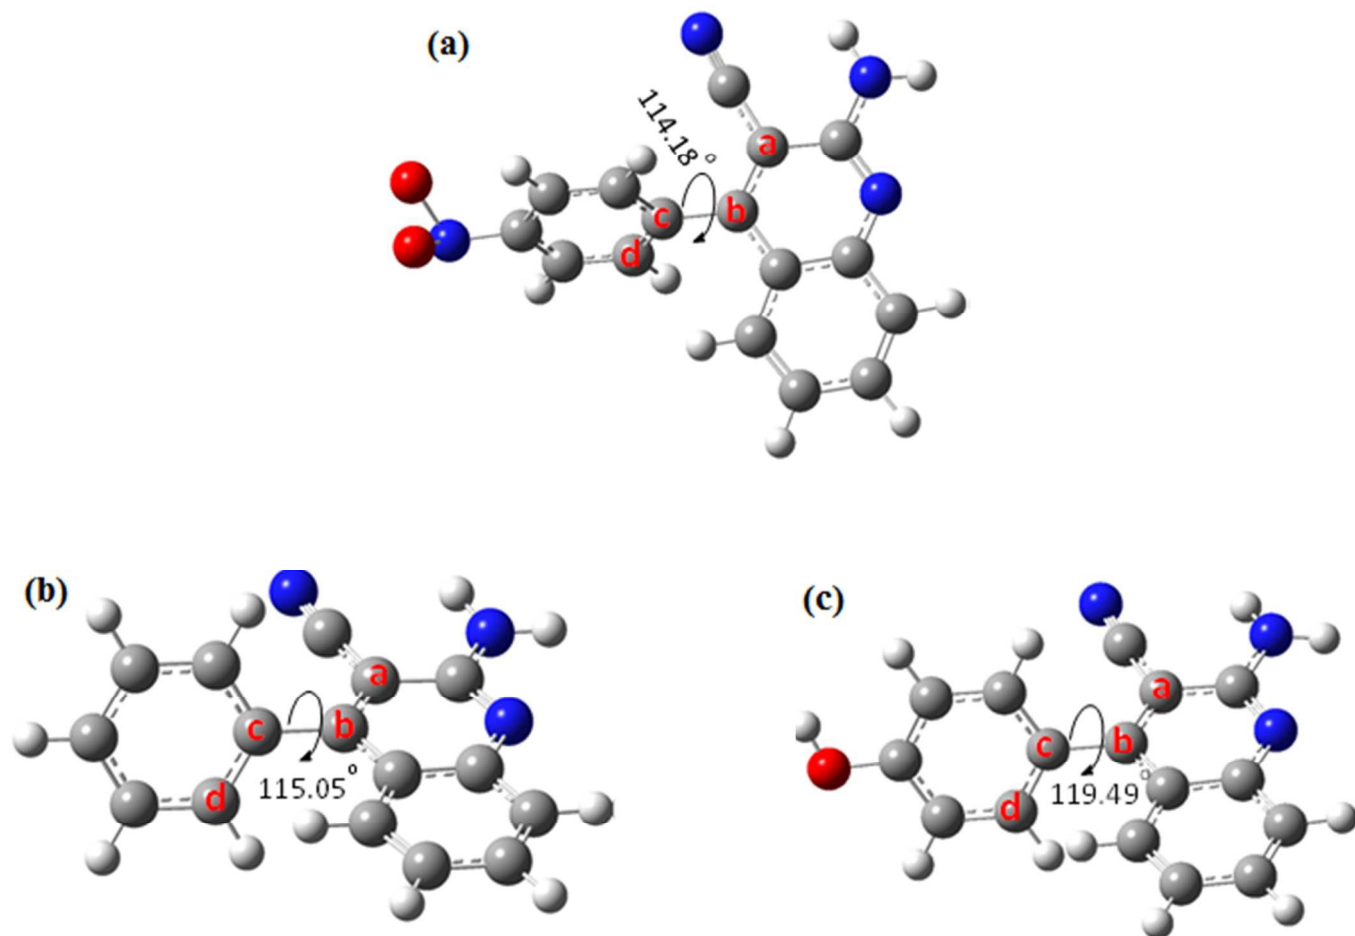
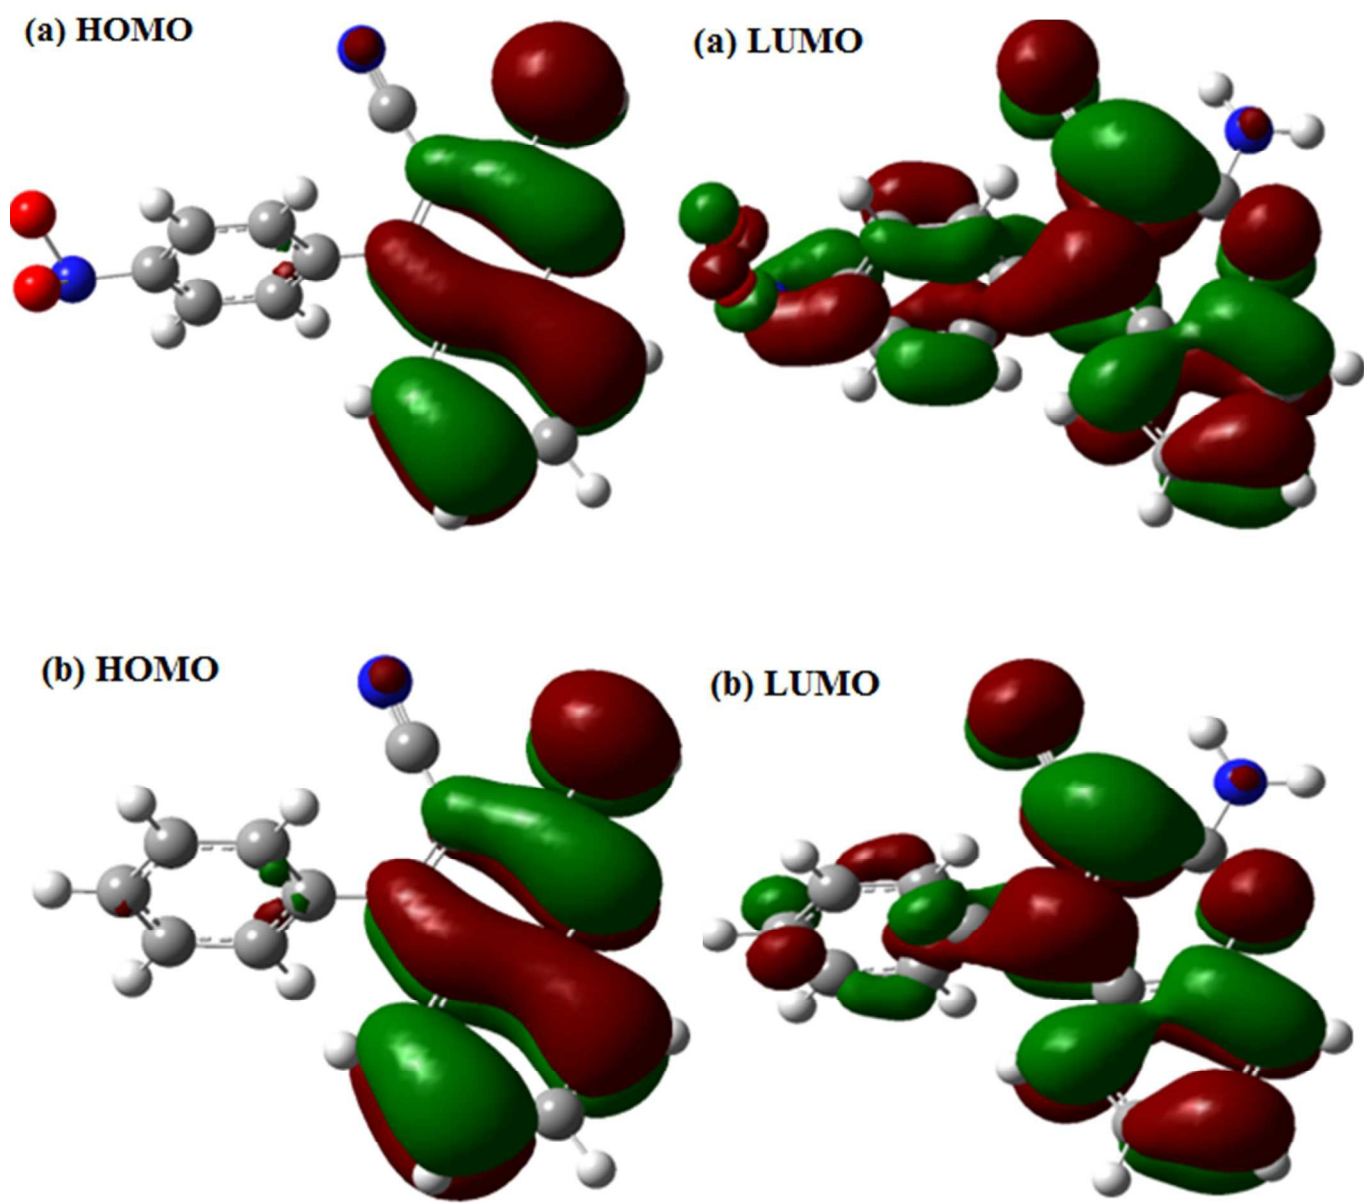


Fig. 11: Optimized molecular structures of the studied compounds showing the dihedral angles a-b-c-d (in degrees).



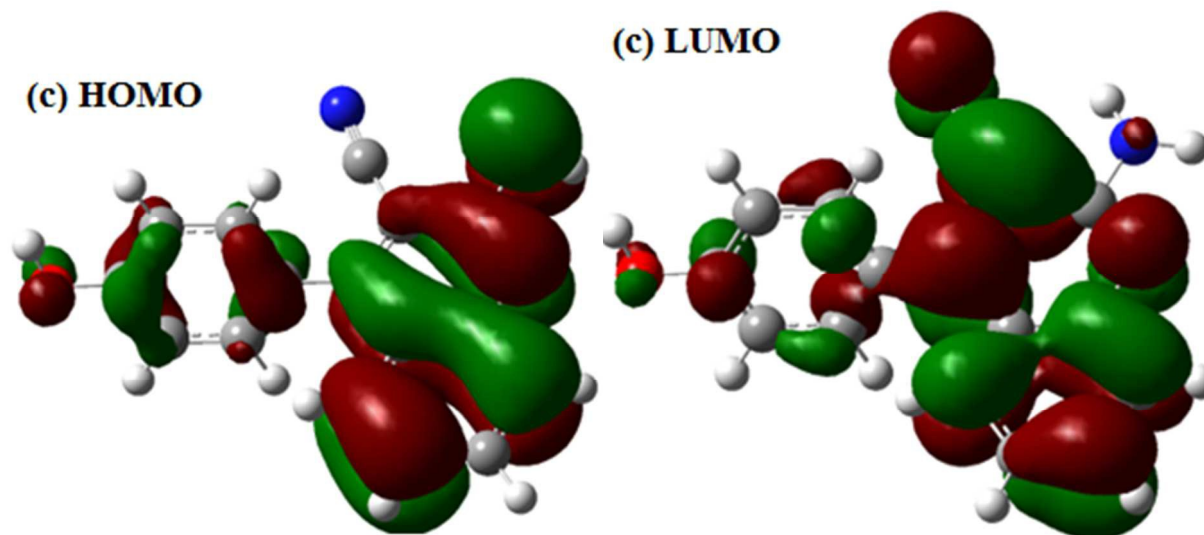


Fig. 12: The frontier molecular orbital of studied AACs (a) AAC-1 (left, HOMO; right, LUMO), (b) AAC-2 (left, HOMO; right, LUMO) and (c) AAC-3 (left, HOMO; right, LUMO)

Table 1. IUPAC name, molecular structure, molecular formula, melting point and analytical data of studied AACs

S.No	IUPAC name and abbreviation of Inhibitor	chemical Structure	molecular formula and M.P. and analytical data
1	2-amino-4-(4-nitrophenyl)quinoline-3-carbonitrile (AAC-1)		C ₁₆ H ₁₀ N ₄ O ₂ (mol. wt. 290.08) Cream colored solid, IR spectrum (KBr cm ⁻¹): 3578, 2858, 2228, 1723, 1680, 1656, 1530, 1448, 1357, 1118, 948, 875, 654, ¹ H NMR (300 MHz, DMSO) δ (ppm): 6.439-6.627, 6.737-6.763, 7.523- 7.848, 8.031,
2	2-amino-4-phenylquinoline-3-carbonitrile (AAC-2)		C ₁₆ H ₁₁ N ₃ , (mol. Wt. 245.09), Brown colored waxy solid, IR spectrum (KBr cm ⁻¹): 3587, 3428, 2871, 2224, 1643, 1503, 1423, 1341, 1154, 924, 735, 652 ¹ H NMR (300 MHz, DMSO) δ (ppm): 6.337-6.527, 6.462-6.635, 7.338-7.536
3	2-amino-4-(4-hydroxyphenyl)quinoline-3-carbonitrile (AAC-3)		C ₁₆ H ₁₁ N ₃ O, (mol. wt. 261.09), yellow colored; IR spectrum (KBr cm ⁻¹): 3646, 3542, 2856, 2245, 1646, 1564, 1472, 1227, 923, 830, 627 ¹ H NMR (300 MHz, DMSO) δ (ppm): 6.468-6.725, 6.635-6.974, 7.896-7.938, 8.323

Table 2: The weight loss parameters obtained for mild steel in 1 M HCl containing different concentrations of AACs

inhibitor	Conc (mgL ⁻¹)	Weight loss (mg)	C _R (mg cm ⁻² h ⁻¹)	Surface coverage (<i>q</i>)	$\eta\%$
Blank	0.0	230	7.66	---	---
AAC-1	10	86	2.86	0.626	62.6
	20	39	1.30	0.8304	83.04
	30	21	0.70	0.9086	90.86
	40	12	0.40	0.9478	94.78
	50	11	0.36	0.9521	95.21
AAC-2	10	64	2.13	0.7217	72.17
	20	28	0.93	0.8782	87.82
	30	17	0.56	0.9260	92.60
	40	10	0.33	0.9565	95.65
	50	9	0.30	0.9608	96.08
AAC-3	10	47	1.56	0.7956	79.56
	20	19	0.63	0.9173	91.73
	30	14	0.46	0.9391	93.91
	40	8	0.26	0.9652	96.52
	50	7	0.23	0.9695	96.95

Table 3: Variation of C_R and η % with temperature in absence and presence of optimum concentration of AACs in 1M HCl

Temperature (K)	Corrosion rate (C_R) ($\text{mg cm}^{-2} \text{h}^{-1}$) and Inhibition efficiency ($\eta\%$)							
	Blank		AAC-1		AAC-2		AAC-3	
	C_R	$\eta\%$	C_R	$\eta\%$	C_R	$\eta\%$	C_R	$\eta\%$
308	7.66	---	0.40	94.77	0.33	95.69	0.26	96.60
318	11.0	---	1.26	88.54	1.06	90.36	0.96	91.27
328	14.3	---	2.43	83.00	1.93	86.50	1.63	88.60
338	18.6	---	4.10	77.95	3.90	79.03	3.63	80.48

Table 4: Values of activation energies for mild steel dissolution in 1M HCl in the absence and at of optimum concentration of AACs

inhibitor	E_a
Blank	28.48
AAC-1	71.40
AAC-2	73.73
AAC-3	75.65

Table 5: The values of K_{ads} and $\Delta G^{\circ}_{\text{ads}}$ for mild steel in absence and presence of optimum concentration of AACs in 1M HCl at different studied temperature

inhibitor	$K_{\text{ads}} (10^4 \text{ M}^{-1})$				$-\Delta G^{\circ}_{\text{ads}} (\text{kJ mol}^{-1})$			
	308	318	328	338	308	318	328	338
AAC-1	2.17	0.92	0.58	0.42	35.87	34.78	34.76	34.62
AAC-2	2.63	1.11	0.77	0.45	36.36	35.36	35.27	34.96
AAC-3	3.32	1.24	0.93	0.49	36.96	35.89	35.56	35.21

Table 6: Tafel polarization parameters for mild steel in 1 M HCl solution in absence and at different concentration of AACs

Inhibitor	Conc Mg/L	E_{corr} (mV/SCE)	β_a ($\mu\text{A}/\text{cm}^2$)	β_c (mV/dec)	i_{corr} (mV/dec)	$\eta\%$	θ
Blank	---	-445	70.5	114.6	1150	----	----
AAC-1	10	-489	79.2	146.4	436.6	62.03	0.6203
	20	-499	77.3	187.5	173.2	84.93	0.8493
	30	-504	77.3	127.8	93.7	91.85	0.9185
	40	-494	85.1	90.8	76.8	93.32	0.9332
AAC-2	10	-499	80.2	103.5	263.9	77.05	0.7705
	20	-458	39.6	52.0	128.3	88.84	0.8884
	30	-491	75.6	82.6	68.5	94.04	0.9404
	40	-510	80.7	116.7	47.1	95.90	0.9590
AAC-3	10	-504	72.2	119.8	213.5	81.43	0.8143
	20	-500	73.1	187.0	86.8	92.45	0.9245
	30	-479	72.1	103.3	53.9	95.31	0.9531
	40	-511	43.4	39.3	17.86	98.44	0.9844

Table 7: EIS parameters obtained for mild steel in 1 M HCl in absence and presence of different concentration of AACs

Inhibitor	Conc Mg/L	R_s ($\Omega \text{ cm}^2$)	R_{ct} ($\Omega \text{ cm}^2$)	n	C_{dl} ($\mu F \text{ cm}^{-2}$)	$\eta\%$	θ
Blank	---	1.12	9.58	0.827	106.21	----	----
AAC-1	10	0.820	24.9	0.857	30.83	61.52	0.6152
	20	0.997	72.3	0.859	76.35	86.74	0.8674
	300	1.510	121.3	0.866	36.40	92.10	0.9210
	40	0.892	167.4	0.873	32.80	94.27	0.9427
AAC-2	10	0.719	40.1	0.859	64.56	76.10	0.7610
	20	1.160	94.7	0.860	34.99	89.88	0.8988
	30	0.649	195.5	0.869	32.15	95.09	0.9509
	40	0.810	244.4	0.885	29.52	96.08	0.9608
AAC-3	10	2.34	51.3	0.863	62.77	81.32	0.8132
	20	0.891	120.5	0.866	34.63	92.04	0.9204
	30	0.76	258.8	0.879	28.47	96.29	0.9629
	40	0.88	371.6	0.886	25.76	97.42	0.9742

Table 8: Percentage atomic contents of elements obtained from EDX spectra for AACs

Inhibitor	Fe	C	N	O
Blank	62.27	34.94	---	2.77
AAC-1	64.86	24.48	5.28	5.34
AAC-2	65.18	26.28	6.37	2.17
AAC-3	63.42	24.87	7.94	3.86

Table 9: Quantum chemical parameters derived from the B3LYP/6-31+G(d,p) method

Parameters→	E_{HOMO}	E_{LUMO}	ΔE	η	χ	ΔN	ΔE_{T}
Inhibitors↓	(eV)	(eV)	(eV)	(eV)	(eV)		
AAC-1	-6.456	-2.584	3.872	1.936	4.520	0.640	-0.484
AAC-2	-6.225	-2.257	3.968	1.984	4.241	0.695	-0.496
AAC-3	-6.114	-2.121	3.993	1.996	4.117	0.722	-0.499