

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Colloidal Nanocrystal Superlattices as Phononic Crystals: Plane Wave Expansion Modeling of Phonon Band Structure†

Seid M. Sadat^a and Robert Y. Wang^{*,a}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Colloidal nanocrystals consist of an inorganic crystalline core with organic ligands bound to the surface and naturally self-assemble into periodic arrays known as superlattices. This periodic structure makes superlattices promising for phononic crystal applications. To explore this potential, we use plane wave expansion methods to model the phonon band structure. We find that the nanoscale periodicity of these superlattices yield phononic band gaps with very high center frequencies on the order of 10^2 GHz. We also find that the large acoustic contrast between the hard nanocrystal cores and the soft ligand matrix lead to very large phononic band gap widths on the order of 10^1 GHz. We systematically vary nanocrystal core diameter, d , nanocrystal core elastic modulus, $E_{NC\ Core}$, interparticle distance (i.e. ligand length), L , and ligand elastic modulus, E_{ligand} , and report on the corresponding effects on the phonon band structure. Our modeling shows that the band gap center frequency increases as d and L are decreased, or as $E_{NC\ Core}$ and E_{ligand} are increased. The band gap width behaves non-monotonically with d , L , $E_{NC\ Core}$, and E_{ligand} , and intercoupling of these variables can eliminate the band gap. Lastly, we observe multiple phononic band gaps in many superlattices and find a correlation between an increase in the number of band gaps and increases in d and $E_{NC\ Core}$. We find that increases in the property mismatch between phononic crystal components (i.e. d/L and $E_{NC\ Core}/E_{ligand}$) flattens the phonon branches and are a key driver in increasing the number of phononic band gaps. Our predicted phononic band gap center frequencies and widths far exceed those in current experimental demonstrations of 3-dimensional phononic crystals. This suggests that colloidal nanocrystal superlattices are promising candidates for use in high frequency phononic crystal applications.

1. Introduction

Phonons are vibrational waves that transport sound and heat.¹ The phononic band diagram (also known as the dispersion relationship) relates the frequency of a given phonon to its corresponding wave vector and is analogous to electronic and photonic band diagrams. By exercising control over the phonon band structure, it is possible to manipulate the transport of sound and heat. One common method of engineering band structure is to create phononic crystals, which are artificially made materials with periodic variations in acoustic impedance (e.g. alternating hard and soft materials). This periodicity results in a phononic band gap that forbids the propagation of phonons in a particular frequency range.²⁻⁵ The phononic crystal is the vibrational wave analogue to the well-known photonic crystal, which uses periodic variations in refractive index to create a photonic band gap.^{6, 7} Two key characteristics of a phononic band gap are its center frequency and its width. The band gap fundamentally arises from wave interference, which requires that the periodicity be

comparable to the phonon wavelength; hence shorter periodicities lead to phononic band gaps with higher center frequencies. The width of the phononic band gap depends on the acoustic impedance ratio of the phononic crystal's components; the further this ratio deviates from unity, the wider the band gap.² Hence a phononic crystal made of alternating hard and soft materials will have a wider band gap than one made of two alternating hard materials. Depending on the number of dimensions in which periodicity occurs, phononic crystals are described as 1-, 2-, or 3-dimensional (i.e. periodic planes, cylinders, and spheres, respectively). Phononic crystals are a promising class of materials for sound and heat manipulation and have been used to create phonon waveguides, cavities, filters, sensors, switches and rectifiers.⁸⁻¹⁴

Phononic crystals are commonly constructed through the assembly of macroscopic building blocks or top-down fabrication methods such as lithography.¹⁵⁻¹⁷ These fabrication approaches have yielded phononic band gaps with center frequencies in the ~ 1 kHz – 10 GHz frequency range. Extending this center frequency range above 10 GHz is desirable because such structures can potentially manipulate heat conduction^{14, 18, 19} and/or enable novel optomechanical devices.²⁰⁻²³ Creating phononic band gaps in this frequency range generally requires nanostructured materials with periodicities of $\lesssim 10$ nm. While 1-dimensional phononic crystals made via sequential thin film deposition have achieved

^a School for Engineering of Matter, Transport & Energy, Arizona State University, Tempe, Arizona 85287, United States of America. E-mail: rywang@asu.edu

† Electronic Supplementary Information (ESI) available: Detailed description of the computational methodology, phononic band gap characteristics as a function of nanocrystal core volume fraction and Poisson's ratio. See DOI: 10.1039/x0xx00000x

band gaps in this frequency range,^{24, 25} creating 3-dimensional periodicities on this length scale is much more difficult. Phononic band gaps with center frequencies above 10 GHz have yet to be experimentally observed in 3-dimensional phononic crystals.^{26, 27}

In this work, we suggest that colloidal nanocrystals can form a natural basis for the bottom-up assembly of 3-dimensional phononic crystals with record high frequency band gaps. Colloidal nanocrystals consist of an inorganic crystalline core with organic ligands (e.g. oleic acid, alkanethiols, etc.) bound to the surface (Figure 1a). Elegant precision and control over colloidal nanocrystal size, shape, and composition has now become commonplace and is summarized in a number of reviews.²⁸⁻³¹ Colloidal nanocrystal-based materials have received attention for a wide range of applications spanning photovoltaics,^{32, 33} light-emitting diodes,^{34, 35} thermoelectrics,³⁶⁻³⁸ thermal storage,³⁹⁻⁴¹ and electronics.^{42, 43} In contrast, the use of colloidal nanocrystals for phononic crystals has received very limited attention.^{44, 45} The diameter of a colloidal nanocrystal core is typically controlled to be between $\sim 2 - 15$ nm, which overlaps nicely with the necessary length-scales needed to achieve phononic band gaps in the $10^1 - 10^2$ GHz frequency range. In addition, van der Waals interactions between the nanocrystal ligand molecules facilitate the self-assembly of colloidal nanocrystals into periodic three-dimensional arrays.^{46, 47} Analogous to the atomic lattice of a crystal, the colloidal nanocrystal community refers to these assemblies as “nanocrystal superlattices.” These superlattices are a natural choice for phononic crystals because their periodic nanocrystal cores and ligand matrix can function as the two components of a phononic crystal (Figure 1b). In addition to having high band gap center frequencies due to small-scale periodicity, colloidal nanocrystal superlattices should also have wide band gaps due to the acoustic contrast between the hard inorganic nanocrystal cores and the soft ligand matrix.

In this work, we use plane wave expansion (PWE) techniques to model the phonon band structure of colloidal nanocrystal superlattices and explore their potential as phononic crystals. Our modeling demonstrates that superlattices can have phononic band gaps with center frequencies on the order of $\sim 10^2$ GHz and band gap widths on the order of $\sim 10^1$ GHz. We also systematically vary nanocrystal core diameter, d , nanocrystal core elastic modulus, E_{NC} , interparticle distance (i.e., ligand length), L , and ligand elastic modulus, E_{ligand} , and report on the corresponding effects on the phonon band structure. Our modeling shows that the band gap center frequency increases as the d and L are decreased, or as E_{NC} and E_{ligand} are increased. The band gap width behaves non-monotonically with d , L , E_{NC} , and E_{ligand} , and intercoupling of these variables can eliminate the band gap. Lastly, we observe multiple phononic band gaps in many superlattices and find a correlation between an increase in the number of band gaps and increases in d and E_{NC} . We find that increases in the property mismatch between phononic crystal components (i.e., d/L and E_{NC}/E_{ligand}) flattens the phonon

branches and is a key driver in increasing the number of phononic band gaps.

2. Methodology

Calculating the phonon band structure requires solving for the phononic crystal's normal modes of vibration and determining their corresponding characteristic frequencies. This is often accomplished using finite difference time domain methods,⁴⁸⁻⁵⁰ finite element methods,^{45, 51, 52} plane wave expansion (PWE) methods,⁵³⁻⁵⁵ and combined molecular dynamics - lattice dynamics approaches.^{44, 56, 57} We utilize the PWE method to determine the phonon band structure in this paper. The PWE method's chief strength is that in-house codes that are computationally inexpensive and adaptable to parallel computation can be written with relative ease. This enables users to achieve maximum control over their computational goals. While many commercial finite element method packages are available, computational flexibility is lost when using these packages. Although molecular dynamics and finite difference time domain methods are also powerful approaches, they suffer from being computationally expensive. In the PWE method, the elastic wave equation is converted into an eigenvalue/eigenvector problem by utilizing the periodicity of the lattice and Bloch's theorem.⁵⁸ Since the eigenvectors and eigenvalues correspond to the phonon wave vectors, \mathbf{k} , and angular frequencies, ω , the PWE method directly yields the phonon band diagram. Our implementation of the PWE method follows the procedure described by Economou and Sigalas.^{53, 59} We begin with the elastic wave equation in three dimensions for a locally isotropic medium:

$$\frac{\partial^2 u^i}{\partial t^2} = \frac{1}{\rho} \left[\frac{\partial}{\partial x_i} \left(\lambda \frac{\partial u^l}{\partial x_l} \right) + \frac{\partial}{\partial x_l} \left(\mu \left[\frac{\partial u^i}{\partial x_l} + \frac{\partial u^l}{\partial x_i} \right] \right) \right] \quad (1)$$

where t is time, i and l are indices (1, 2, or 3), and u^i , u^l , x_i and x_l are the Cartesian components of the displacement vector, $\mathbf{u}(\mathbf{r})$, and position vector, \mathbf{r} , respectively. The spatially varying density, first Lamé coefficient, and second Lamé coefficient are represented by $\rho(\mathbf{r})$, $\lambda(\mathbf{r})$ and $\mu(\mathbf{r})$, respectively. Since phononic crystals are periodic, the local material properties are also periodic and can be expressed using a spatial Fourier series for the primitive unit cell.

$$\rho(\mathbf{r}) = \sum_{\mathbf{G}} \rho_{\mathbf{G}} e^{j\mathbf{G}\cdot\mathbf{r}} \quad (2a)$$

$$\lambda(\mathbf{r}) = \sum_{\mathbf{G}} \lambda_{\mathbf{G}} e^{j\mathbf{G}\cdot\mathbf{r}} \quad (2b)$$

$$\mu(\mathbf{r}) = \sum_{\mathbf{G}} \mu_{\mathbf{G}} e^{j\mathbf{G}\cdot\mathbf{r}} \quad (2c)$$

where \mathbf{G} is a reciprocal lattice vector, j is the imaginary unit, and subscript \mathbf{G} refers to the \mathbf{G} th Fourier component of the indicated property. Since all of the coefficients in the elastic wave equation are periodic, we can employ Bloch's theorem to write:

$$\mathbf{u}(\mathbf{r}) = u_{\mathbf{k}}(\mathbf{r}) e^{j\mathbf{k}\cdot\mathbf{r}} = \sum_{\mathbf{G}} u_{\mathbf{k}+\mathbf{G}} e^{j(\mathbf{k}+\mathbf{G})\cdot\mathbf{r}} \quad (3)$$

which has plane wave solutions in the form of:

$$\mathbf{u} = e^{j(\mathbf{k}\cdot\mathbf{r} - \omega t)} \quad (4)$$

Equations 1 – 4 can be combined to yield the following eigenvalue problem:⁵³

$$\omega^2 u_{\mathbf{k}_0+\mathbf{G}}^i = \sum_{\mathbf{G}'} \left[\sum_{l, \mathbf{G}''} \rho_{\mathbf{G}-\mathbf{G}''}^{-1} [\lambda_{\mathbf{G}''-\mathbf{G}'}(\mathbf{k}_0 + \mathbf{G}')_l (\mathbf{k}_0 + \mathbf{G}'')_l + \mu_{\mathbf{G}''-\mathbf{G}'}(\mathbf{k}_0 + \mathbf{G}')_l (\mathbf{k}_0 + \mathbf{G}'')_l] u_{\mathbf{k}_0+\mathbf{G}'}^l + \sum_{\mathbf{G}''} (\rho_{\mathbf{G}-\mathbf{G}''}^{-1} \mu_{\mathbf{G}''-\mathbf{G}'} \sum_n (\mathbf{k}_0 + \mathbf{G}')_n (\mathbf{k}_0 + \mathbf{G}'')_n) u_{\mathbf{k}_0+\mathbf{G}'}^n \right] \quad (5)$$

where \mathbf{k}_0 is a wave vector, \mathbf{G}, \mathbf{G}' and \mathbf{G}'' are reciprocal lattice vectors, and i, l , and n are indices that vary between 1, 2, and 3. If the dimensions and mechanical properties of a phononic crystal's constituent phases are specified, Equation 5 can be rewritten in matrix form and solved to obtain the eigenfrequencies, ω , of the eigenvector, \mathbf{k}_0 . Varying \mathbf{k}_0 throughout the Brillouin zone then allows the phonon band diagram to be mapped out. Whereas the above equations are written in terms of λ and μ , experimental measurements on the mechanical properties of nanocrystal superlattices have generally been reported in terms of the bulk modulus, B , and elastic modulus, E .⁶⁰⁻⁶² If Poisson's ratio, ν , is known, then bulk moduli can be converted into elastic moduli. In addition, the mechanical property set of E and ν can be transformed into λ and μ via the following relations:⁶³

$$\mu = \frac{E}{2(1+\nu)} \quad (6a)$$

$$\lambda = \frac{\nu \times E}{(1+\nu) \times (1-2\nu)} \quad (6b)$$

To apply the PWE method to colloidal nanocrystal superlattices we consider the nanocrystal cores and nanocrystal ligands as the two components of a phononic crystal (i.e. a periodic arrangement of inorganic spheres embedded in ligand matrix). We focus our modeling effort on face-centered-cubic lattices because this is the arrangement that colloidal nanocrystal superlattices most commonly adopt.⁶¹ Figure 2 illustrates the conventional unit cell, primitive unit cell, and first Brillouin zone of a face-centered cubic lattice with nanocrystal diameter, d , interparticle distance, L , and lattice constant, a .

Of the many varieties of colloidal nanocrystal superlattices, the most complete set of experimentally measured mechanical properties correspond to superlattices consisting of PbS nanocrystals with oleic acid ligands.⁶⁰⁻⁶² Consequently we initiate our phonon band diagram discussion on this particular superlattice (Figure 3), and use input values of interparticle distance, $L = 1.5$ nm, nanocrystal core elastic modulus, $E_{\text{NC core}} = 54$ GPa, ligand matrix elastic modulus, $E_{\text{ligand}} = 2.6$ GPa, nanocrystal core density, $\rho_{\text{NC core}} = 7600$ kg/m³, ligand matrix density, $\rho_{\text{ligand}} = 895$ kg/m³, nanocrystal core Poisson's ratio, $\nu_{\text{NC core}} = 1/3$, and ligand matrix Poisson's ratio, $\nu_{\text{ligand}} = 1/3$. Unless otherwise stated, these parameters are used in all of this paper's calculations.

Since the PWE method assumes that the phonon medium can be treated as a continuum, there is a maximum frequency and

minimum length scale for which it is valid. Past studies have shown that continuum methods can reasonably predict phonon band structures up to a frequency of ~ 1 THz.^{64, 65} To stay well below this threshold, we limit our model to frequencies ≤ 500 GHz. Furthermore, the shortest phonon wavelength considered in our calculations is 37.9 Å (this corresponds to the W point in the Brillouin zone for a nanocrystal core diameter of 2 nm and interparticle distance of 1 nm). This phonon wavelength is an order of magnitude larger than typical interatomic distances and represents a reasonable threshold for applying continuum approximations. Our use of the elastic wave equation implicitly assumes that the mechanical response of the material is within the linear regime, which means that our model only considers small vibrational wave amplitudes. The PWE method also uses periodic boundary conditions, which is equivalent to having perfect superlattice order. The primary effect of superlattice disorder would be to introduce phonon scattering sites and/or localized phonons (i.e. phonons that are not plane waves) that are not captured in the band diagram. In addition to the physical approximations of our methodology, numerical accuracy of our code is also important. To confirm our accuracy, we have checked it for computational convergence and benchmarked it against other PWE results in the literature (see Figure S2). Additional details on the computational methodology used in this work are available in the Electronic Supplementary Information.

3. Results and Discussion

Figure 3 shows the phonon band diagram for a superlattice consisting of PbS nanocrystals with oleic acid ligands and illustrates that these materials can have wide phononic band gaps with center frequencies in the 100 GHz-range. Phononic crystals with 3-dimensional periodicity commonly have band gaps that exist only along particular crystallographic directions. A band gap that exists in every direction is less common and is referred to as an "absolute" or "complete" band gap.⁶⁶ Figure 3 shows that the PbS nanocrystal – oleic acid ligand superlattice exhibits this less common feature. The phonon branches that intersect the Γ point at the origin are known as "acoustic" branches whereas those that intersect the Γ point at non-zero frequency are known as "optical" branches. These branches appear in groups of three due to the three mechanical degrees of freedom. In typical atomic crystals (e.g. bulk GaP, AlAs, GaSb, etc.), the band gap commonly resides in between the acoustic phonon branches and the first set of optical branches. In contrast, the phononic band gap in the nanocrystal superlattice falls in between the first and second set of optical branches. Accompanying this band gap characteristic is a strong frequency overlap between the first set of optical phonon branches and the acoustic branches. This frequency overlap creates a large phase space for phonon-phonon scattering processes that satisfy scattering selection rules (i.e., conservations of energy and crystal momentum). This large phase space in turn creates opportunities for fast energy transfer between acoustic and optical phonons.

Furthermore, since optical phonons interact with light and acoustic phonons do not, this frequency resonance between the optical and acoustic phonons suggests that fast energy transfer between photons and acoustic phonons can occur in nanocrystal superlattices.

We next discuss the effect of changing the nanocrystal core diameter, interparticle distance, and colloidal nanocrystal mechanical properties on the phonon band structure. In principle, there are eight phononic crystal variables, d , L , $E_{NC\ core}$, E_{ligand} , $\rho_{NC\ core}$, ρ_{ligand} , $v_{NC\ core}$, and v_{ligand} . We vary the nanocrystal core through a typical colloidal nanocrystal diameter range of 2 – 15 nm. The interparticle distance in a nanocrystal superlattice is controlled by the organic ligands on the nanocrystal core surface. These ligands are typically small organic molecules such as oleic acid and alkanethiols. Consequently we vary the interparticle distance and matrix elastic modulus from 1 – 3 nm and 1 – 8 GPa, respectively, which are ranges that are representative of typical organic ligands. Since a very wide variety of nanocrystal core compositions are possible,²⁸⁻³¹ we vary the elastic modulus of the nanocrystal core over a large range of 10 – 1250 GPa. We found that varying Poisson's ratio had only a minor effect on the phononic band gap characteristics, and we therefore leave out discussion of this parameter (Figure S6 in Electronic Supplementary Information). Inspection of Equations 5 and 6 reveal that density only shows up as a denominator for the elastic modulus and Poisson's ratio (i.e. E/ρ and v/ρ). Since Poisson's ratio has only a minor effect on the band gap characteristics, the effect of varying density can be inferred by rescaling our results for varying elastic modulus. Phononic crystals are often described in terms of their volume fraction of matrix inclusions, which in our case corresponds to the nanocrystal core volume fraction. Since our calculations vary both nanocrystal core diameter and interparticle distance (which is directly related to ligand length, see Figure 1), our calculations implicitly span a nanocrystal core volume fraction range of 4.7% to 61.0%. Lastly, we note that in some cases we observe multiple phononic band gaps were observed (see below); however, the most prominent band gap is the gap occurring between the first and second set of optical branches. Unless otherwise stated, the following discussion focuses on this band gap.

Figure 4a shows that decreasing the nanoparticle diameter and/or interparticle distance increases the center frequency of the band gap. This behavior arises because the center frequencies of phononic band gaps correspond to wavelengths that satisfy the Bragg condition (i.e., constructive interference of scattered waves from a periodic medium). Decreasing the nanoparticle diameter and/or interparticle distance decreases the unit cell length, which decreases the Bragg wavelength and increases the center frequency. The impact of changing interparticle distance on the center frequency is most pronounced at smaller nanoparticle diameters. This is because interparticle distance changes lead to large relative changes in unit cell sizes in this diameter regime. For large nanoparticle diameters, the effect of interparticle distance on center frequency is small because the unit cell size is dominated by

the nanoparticle diameter. The band gap width can go to zero when combining small nanocrystal diameters with large interparticle distances and so we do not plot center frequencies in these instances (Figure 4a).

As the elastic modulus of the ligand matrix or nanocrystal core is increased, the center frequency of the phononic band gap increases monotonically (Figure 4b and 4c). Although the band gap center frequency increases in all cases, the magnitude of this increase is size dependent and depends on whether the modulus of the nanocrystal core or ligand matrix is changing. The ligand modulus has the greatest impact on the band gap center frequency at small nanoparticle diameters (Figure 4b). This is intuitive because the ligands make up the greatest fraction of the unit cell when the nanoparticle diameters are small. Analogously, the nanocrystal core modulus has the greatest impact at large nanoparticle diameters because this is when the nanocrystal cores make up the largest fraction of the unit cell (Figure 4c). Notably the band gap disappears at large diameters when the nanocrystal core modulus is very soft or very hard. For example, we do not observe band gaps above 9 and 13 nm diameters for nanocrystal core moduli of 1250 and 10 GPa, respectively.

The acoustic contrast between the soft ligand matrix and hard nanocrystal cores leads to large band gap widths of up to ~ 130 GHz for 2 nm diameters and 1 nm interparticle distances (Figure 5a). Interestingly, we observe a non-monotonic relationship between band gap width and nanoparticle diameter. The band gap width first rises with increasing diameter, reaches a maximum value at a critical diameter, d_{crit} , and then decreases. One implication of this non-monotonic behavior is that not all colloidal nanocrystal superlattices will have phononic band gaps. For example, our model predicts the absence of a phononic band gap for nanocrystal diameters below 4 nm with an interparticle distance of 3.0 nm.

The combined effects of d , L , E_{ligand} , and $E_{NC\ core}$ on phononic band gap width can be visualized in Figures 5a, 5b, and 5c. These figures collectively reveal an intricate and rich behavior between these parameters and phononic band gap width. This behavior is best visualized in Figure 5c, which shows the relationship between phononic band gap width and nanocrystal core diameter for a large range of $E_{NC\ core}$, 10 – 1250 GPa. In addition to an increasing band gap width below d_{crit} and a decreasing band gap width above d_{crit} , a second non-monotonic behavior is observed in Figure 5c. For nanocrystal core diameters 4 nm and larger, we see that the band gap width first increases with increasing $E_{NC\ core}$, reaches a maximum, and then decreases with increasing $E_{NC\ core}$. For example, nanocrystal core diameters of 8 nm have an increasing band gap width for $10\text{ GPa} < E_{NC\ core} < 170\text{ GPa}$ and decreasing band gap width for $170\text{ GPa} < E_{NC\ core} < 1250\text{ GPa}$. This behavior causes the right sides of the curves in Figure 5c to first sweep diagonally up and then sweep diagonally down as $E_{NC\ core}$ is changed from 10 to 1250 GPa. A similar, but subtler behavior can be seen in Figures 5a and 5b. The subtlety of this behavior for changes in L and E_{ligand} in Figure 5 arises because these parameters span a more narrow range than $E_{NC\ core}$.

The fact that band gap width increases, reaches a maximum, and then decreases as d , L , E_{ligand} , and $E_{\text{NC core}}$ are varied suggests that these four parameters impact band gap width in similar manners. This type of behavior has also been observed by Zanjani and Lukes,⁴⁵ who found that as interparticle distance increased, the phononic band gap width increased, reached a maximum, and then decreased. They explained the origin of this behavior by studying the Bragg frequencies of each phononic crystal component and utilizing a transfer matrix model. Their modeling found that as the Bragg frequency mismatch between the two components increased, the band gap first widened, then reached a maximum at moderate Bragg frequency separation, and then narrowed. Since Bragg frequency is proportional to the square root of elastic modulus and inversely proportional to length, this Bragg frequency explanation can also explain our observed effects of elastic modulus on phononic band gap width. The four parameters varied in Figure 5, d , L , E_{ligand} , and $E_{\text{NC core}}$, all have similar effects on the band gap width because each parameter has a role in determining the overall Bragg frequency mismatch between the nanocrystal cores and ligand matrix. In effect, the band gap width data in Figure 5 represents slices of a surface in a 4-dimensional space (i.e. d , L , E_{ligand} , and $E_{\text{NC core}}$).

In many instances, we observe multiple band gaps in the phonon band diagram (Figures 6 and 7). The band gap between the first and second set of optical branches tends to be the widest and higher frequency band gaps tend to be much more narrow. Our data also shows a correlation between increases in nanocrystal core diameter and the number of band gaps (Figures 6a and 6c) and increases in the nanocrystal core elastic modulus and the number of band gaps (Figures 6b and 6d). The origins of these correlations can be explained by observing the band diagram characteristics for changes in nanocrystal core diameter (Figures 7a – 7c) and nanocrystal core elastic modulus (Figure 7d – 7f). It is well known that increasing property mismatches causes flattening of the phonon dispersion branches.⁶⁷ The effects of increasing nanocrystal core diameter and increasing nanocrystal core elastic modulus are to increase mismatch with the ligand matrix (i.e. d / L and $E_{\text{NC core}} / E_{\text{ligand}}$ increase). As the phonon branches flatten, this leads to more opportunities to form phononic band gaps and hence we observe a correlation between an increase in the number of band gaps and an increase in nanocrystal core diameter and elastic modulus.

Another notable effect of changing nanocrystal core diameter and elastic modulus on the phonon band diagram is a re-scaling of the frequencies. While this frequency re-scaling leads to meaningful changes in the phonon band structure, its effects on the number of observed band gaps are artificial in nature. When downshifting the frequencies, one effect is the appearance of seemingly more phonon branches. However this apparent effect originates from our maximum frequency limitation of 500 GHz due to the continuum nature of our PWE model. These “new branches” are simply shifting from frequencies above 500 GHz to frequencies below 500 GHz. Another effect of this frequency re-scaling is the potential to

flatten bands as the frequencies are downscaled. While one might assume that this frequency re-scaling could be the origin of band flattening described in the above paragraph, it should be noted that band flattening due to frequency re-scaling and band flattening due to property mismatches are independent effects. This is evident when inspecting Figure 7f, which simultaneously has the flattest optical bands and the least frequency downscaling.

4. Conclusions

The results in this work illustrate that colloidal nanocrystals are excellent candidates for the bottom-up assembly of 3-dimensional phononic crystals. The nanoscale periodicity and acoustic contrast between the hard nanocrystal cores and soft ligand matrix lead to phononic band gaps with center frequencies on the order of $\sim 10^2$ GHz and band gap widths on the order of $\sim 10^1$ GHz. In addition, these characteristics can be tuned by changing the nanocrystal core diameter, nanocrystal core elastic modulus, interparticle distance, and ligand modulus. These results suggest that colloidal nanocrystal superlattices are promising candidates for use in high frequency phononic crystal applications that exert control over sound and heat.

Acknowledgements

This work was supported by the Young Investigator Research Program of the Air Force Office of Scientific Research through award FA9550-13-1-0163 and by the National Science Foundation through award number CBET-1227979. We would like to thank ASU Research Computing for providing the computational resources Saguaro and Ocotillo clusters for carrying out the current work. We also thank Michael Sigalas for helpful discussions.

References

- 1 M. Maldovan, *Nature*, 2013, **503**, 209-217.
- 2 T. Gorishnyy, M. Maldovan, C. Ullal and E. Thomas, *Phys. World*, 2005, **18**, 24-29.
- 3 M.-H. Lu, L. Feng and Y.-F. Chen, *Materials Today*, 2009, **12**, 34-42.
- 4 R. Olsson Iii and I. El-Kady, *Measurement Science and Technology*, 2009, **20**, 012002.
- 5 Y. Pennec, J. O. Vasseur, B. Djafari-Rouhani, L. Dobrzyński and P. A. Deymier, *Surface Science Reports*, 2010, **65**, 229-291.
- 6 M. M. Hossain and M. Gu, *Laser & Photonics Reviews*, 2014, **8**, 233-249.
- 7 S. John, *Physical Review Letters*, 1987, **58**, 2486-2489.
- 8 H. Chen and C. T. Chan, *Journal of Physics D: Applied Physics*, 2010, **43**, 113001.
- 9 R. H. O. III and I. El-Kady, *Measurement Science and Technology*, 2009, **20**, 012002.
- 10 A. Khelif, A. Choujaa, B. Djafari-Rouhani, M. Wilm, S. Ballandras and V. Laude, *Physical Review B*, 2003, **68**, 214301.
- 11 J.-H. Sun and T.-T. Wu, *Physical Review B*, 2005, **71**, 174303.

- 12 S. Yang, J. H. Page, Z. Liu, M. L. Cowan, C. T. Chan and P. Sheng, *Physical Review Letters*, 2004, **93**, 024301.
- 13 N. Boechler, G. Theocharis and C. Daraio, *Nat Mater*, 2011, **10**, 665-668.
- 14 M. Maldovan, *Physical Review Letters*, 2013, **110**, 025902.
- 15 R. Martinez-Sala, J. Sancho, J. V. Sanchez, V. Gomez, J. Llinares and F. Meseguer, *Nature*, 1995, **378**, 241-241.
- 16 F. R. Montero de Espinosa, E. Jiménez and M. Torres, *Physical Review Letters*, 1998, **80**, 1208-1211.
- 17 T. Gorishnyy, C. Ullal, M. Maldovan, G. Fytas and E. Thomas, *Physical review letters*, 2005, **94**, 115501.
- 18 S. Alaie, D. F. Goettler, M. Su, Z. C. Leseman, C. M. Reinke and I. El-Kady, *Nat Commun*, 2015, **6**, 7228.
- 19 N. Zen, T. A. Puurtinen, T. J. Isotalo, S. Chaudhuri and I. J. Maasilta, *Nat Commun*, 2014, **5**, 3435.
- 20 H. Shin, J. A. Cox, R. Jarecki, A. Starbuck, Z. Wang and P. T. Rakich, *Nat Commun*, 2015, **6**, 6427.
- 21 J. Gomis-Bresco, D. Navarro-Urrios, M. Oudich, S. El-Jallal, A. Griol, D. Puerto, E. Chavez, Y. Pennec, B. Djafari-Rouhani, F. Alzina, A. Martínez and C. M. S. Torres, *Nat Commun*, 2014, **5**, 4452.
- 22 A. Fainstein, N. D. Lanzillotti-Kimura, B. Jusserand and B. Perrin, *Physical Review Letters*, 2013, **110**, 037403.
- 23 M. Eichenfield, J. Chan, R. M. Camacho, K. J. Vahala and O. Painter, *Nature*, 2009, **462**, 78-82.
- 24 V. Narayanamurti, H. L. Störmer, M. A. Chin, A. C. Gossard and W. Wiegmann, *Physical Review Letters*, 1979, **43**, 2012-2016.
- 25 O. Koblinger, J. Mebert, E. Dittrich, S. Döttinger, W. Eisenmenger, P. V. Santos and L. Ley, *Physical Review B*, 1987, **35**, 9372-9375.
- 26 W. Cheng, J. Wang, U. Jonas, G. Fytas and N. Stefanou, *Nat Mater*, 2006, **5**, 830-836.
- 27 E. Alonso-Redondo, M. Schmitt, Z. Urbach, C. M. Hui, R. Sainidou, P. Rembert, K. Matyjaszewski, M. R. Bockstaller and G. Fytas, *Nat Commun*, 2015, **6**, 8309.
- 28 C. B. Murray, C. Kagan and M. Bawendi, *Annual Review of Materials Science*, 2000, **30**, 545-610.
- 29 J. Park, J. Joo, S. G. Kwon, Y. Jang and T. Hyeon, *Angewandte Chemie International Edition*, 2007, **46**, 4630-4660.
- 30 Y. Xia, Y. Xiong, B. Lim and S. E. Skrabalak, *Angewandte Chemie International Edition*, 2009, **48**, 60-103.
- 31 M. V. Kovalenko, L. Manna, A. Cabot, Z. Hens, D. V. Talapin, C. R. Kagan, V. I. Klimov, A. L. Rogach, P. Reiss, D. J. Milliron, P. Guyot-Sionnest, G. Konstantatos, W. J. Parak, T. Hyeon, B. A. Korgel, C. B. Murray and W. Heiss, *ACS Nano*, 2015, **9**, 1012-1057.
- 32 S. A. Mcdonald, G. Konstantatos, S. Zhang, P. W. Cyr, E. J. Klem, L. Levina and E. H. Sargent, *Nature materials*, 2005, **4**, 138-142.
- 33 C.-H. M. Chuang, P. R. Brown, V. Bulović and M. G. Bawendi, *Nature materials*, 2014, **13**, 796.
- 34 X. Dai, Z. Zhang, Y. Jin, Y. Niu, H. Cao, X. Liang, L. Chen, J. Wang and X. Peng, *Nature*, 2014, **515**, 96-99.
- 35 K.-S. Cho, E. K. Lee, W.-J. Joo, E. Jang, T.-H. Kim, S. J. Lee, S.-J. Kwon, J. Y. Han, B.-K. Kim and B. L. Choi, *Nature Photonics*, 2009, **3**, 341-345.
- 36 R. Y. Wang, J. P. Feser, J.-S. Lee, D. V. Talapin, R. Segalman and A. Majumdar, *Nano letters*, 2008, **8**, 2283-2288.
- 37 F.-J. Fan, B. Yu, Y.-X. Wang, Y.-L. Zhu, X.-J. Liu, S.-H. Yu and Z. Ren, *Journal of the American Chemical Society*, 2011, **133**, 15910-15913.
- 38 F. J. Fan, Y. X. Wang, X. J. Liu, L. Wu and S. H. Yu, *Advanced Materials*, 2012, **24**, 6158-6163.
- 39 M. Liu and R. Y. Wang, *Scientific reports*, 2015, **5**, 16353.
- 40 M. Liu and R. Y. Wang, *Nanoscale*, 2013, **5**, 7234-7237.
- 41 M. Liu, Y. Ma, H. Wu and R. Y. Wang, *ACS Nano*, 2015, **9**, 1341-1351.
- 42 S. J. Oh, Z. Wang, N. E. Berry, J.-H. Choi, T. Zhao, E. A. Gaulding, T. Paik, Y. Lai, C. B. Murray and C. R. Kagan, *Nano letters*, 2014, **14**, 6210-6216.
- 43 M. E. Turk, J.-H. Choi, S. J. Oh, A. T. Fafarman, B. T. Diroll, C. B. Murray, C. R. Kagan and J. M. Kikkawa, *Nano letters*, 2014, **14**, 5948-5952.
- 44 M. B. Zanjani and J. R. Lukes, *Journal of Applied Physics*, 2014, **115**, 143515.
- 45 M. B. Zanjani and J. R. Lukes, *The Journal of Physical Chemistry C*, 2015, **119**, 16889-16896.
- 46 E. Shevchenko, D. Talapin, A. Kornowski, F. Wiekhorst, J. Kotzler, M. Haase, A. Rogach and H. Weller, *Advanced Materials*, 2002, **14**, 287.
- 47 D. V. Talapin, E. V. Shevchenko, A. Kornowski, N. Gaponik, M. Haase, A. L. Rogach and H. Weller, *Advanced Materials*, 2001, **13**, 1868.
- 48 N. Aravantinos-Zafiris and M. Sigalas, *Journal of Vibration and Acoustics*, 2013, **135**, 041003.
- 49 J.-H. Sun and T.-T. Wu, *Physical Review B*, 2007, **76**, 104304.
- 50 P.-F. Hsieh, T.-T. Wu and J.-H. Sun, *Ultrasonics, Ferroelectrics, and Frequency Control, IEEE Transactions on*, 2006, **53**, 148-158.
- 51 P. Jiang, X.-P. Wang, T.-N. Chen and J. Zhu, *Journal of Applied Physics*, 2015, **117**, 154301.
- 52 B. Graczykowski, M. Sledzinska, F. Alzina, J. Gomis-Bresco, J. S. Reparaz, M. R. Wagner and C. M. Sotomayor Torres, *Physical Review B*, 2015, **91**, 075414.
- 53 E. N. Economou and M. Sigalas, *The Journal of the Acoustical Society of America*, 1994, **95**, 1734-1740.
- 54 M. Kafesaki, M. M. Sigalas and E. N. Economou, *Solid State Communications*, 1995, **96**, 285-289.
- 55 M. S. Kushwaha, P. Halevi, L. Dobrzynski and B. Djafari-Rouhani, *Physical Review Letters*, 1993, **71**, 2022-2025.
- 56 R. Meyer, *arXiv preprint arXiv:1511.00739*, 2015.
- 57 J.-W. Jiang, *Nanoscale*, 2014, **6**, 8326-8333.
- 58 D. Sjöberg, C. Engström, G. Kristensson, D. J. Wall and N. Wellander, *Multiscale Modeling & Simulation*, 2005, **4**, 149-171.
- 59 H. Ibach, H. Lüth, L. Mihaly and D. Mandrus, *American Journal of Physics*, 1992, **60**, 1053-1054.
- 60 K. Bian, W. Bassett, Z. Wang and T. Hanrath, *The Journal of Physical Chemistry Letters*, 2014, **5**, 3688-3693.
- 61 P. Podsiadlo, G. Krylova, B. Lee, K. Critchley, D. J. Gosztola, D. V. Talapin, P. D. Ashby and E. V. Shevchenko, *Journal of the American Chemical Society*, 2010, **132**, 8953-8960.
- 62 P. Podsiadlo, B. Lee, V. B. Prakapenka, G. V. Krylova, R. D. Schaller, A. Demortière and E. V. Shevchenko, *Nano Letters*, 2011, **11**, 579-588.
- 63 R. G. Budynas, *Advanced strength and applied stress analysis*, McGraw-Hill Science/Engineering/Math, 1998.
- 64 D. Cheney, 2013.
- 65 D. A. Cheney and J. R. Lukes, *Journal of Heat Transfer*, 2013, **135**, 091101.
- 66 G. Taras, M. Martin, U. Chaitanya and T. Edwin, *Physics World*, 2005, **18**, 24.
- 67 N. W. Ashcroft and N. D. Mermin, *Appendix N*, 2010.

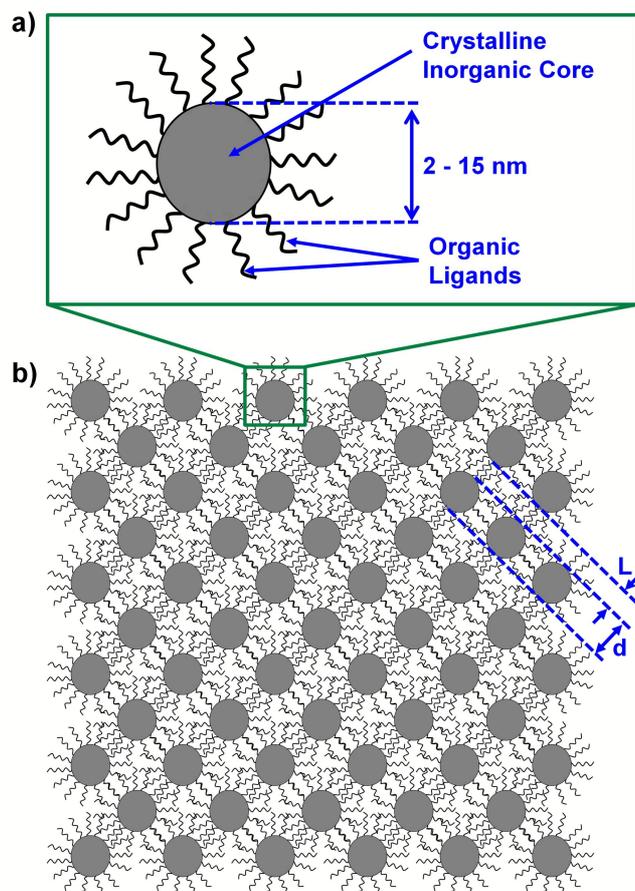


Figure 1. Schematics of (a) an individual colloidal nanocrystal and (b) a face-centered cubic colloidal nanocrystal superlattice as viewed along the [100] direction. An individual colloidal nanocrystal consists of a crystalline inorganic core with organic ligands on its surface (e.g. oleic acid, alkanethiols, etc.). When colloidal nanocrystals are assembled into a superlattice, they form a phononic crystal that consists of a periodic array of hard nanocrystal cores embedded in a soft ligand matrix. The two key length scales in the phononic crystal are the diameter of the inorganic nanocrystal core, d , and the interparticle distance, L . The interparticle distance is primarily determined by the ligand length.

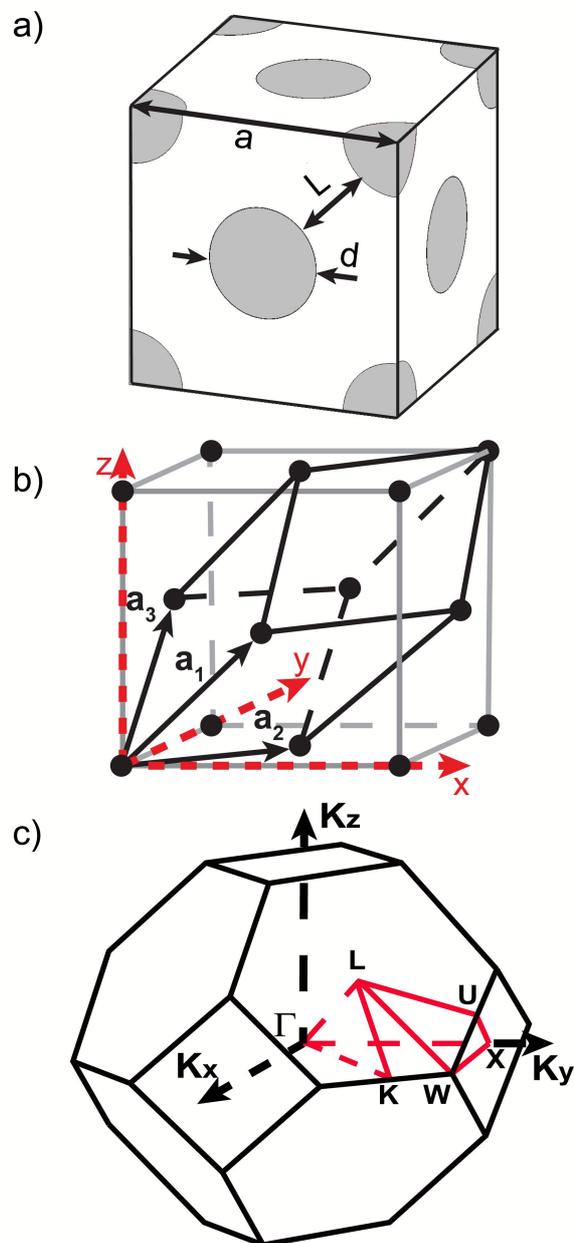


Figure 2. (a) Schematic of the conventional unit cell for a face-centered cubic lattice with relevant geometrical parameters labeled: interparticle distance, L , lattice constant, a , and nanocrystal core diameter, d . (b) Schematic of a primitive unit cell for a face-centered cubic lattice and corresponding primitive lattice vectors, \mathbf{a}_1 , \mathbf{a}_2 , and \mathbf{a}_3 . (c) Schematic of the first Brillouin zone (black lines) and the irreducible region of the first Brillouin zone (red lines).

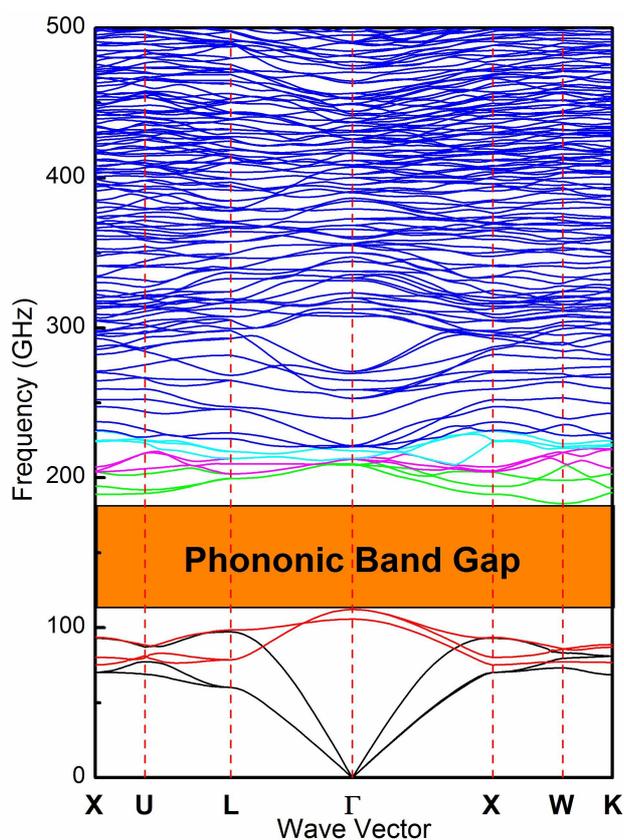


Figure 3. Phononic band diagram of a face-centered cubic colloidal nanocrystal superlattice comprised of PbS nanocrystals ($E = 54$ GPa, $\nu = 1/3$, and $\rho = 7600$ kg/m³) with oleic acid ligands ($E = 2.6$ GPa, $\nu = 1/3$, and $\rho = 895$ kg/m³). The nanocrystal core diameter and interparticle distance in this band diagram are $d = 5$ nm and $L = 1.5$ nm. To improve clarity, the first 5 sets of branches (i.e., 15 branches) are color-coded. The three acoustic branches are black, the first set of optical branches are red, the second set of optical branches are green, and subsequent sets of optical branches are purple and cyan, respectively.

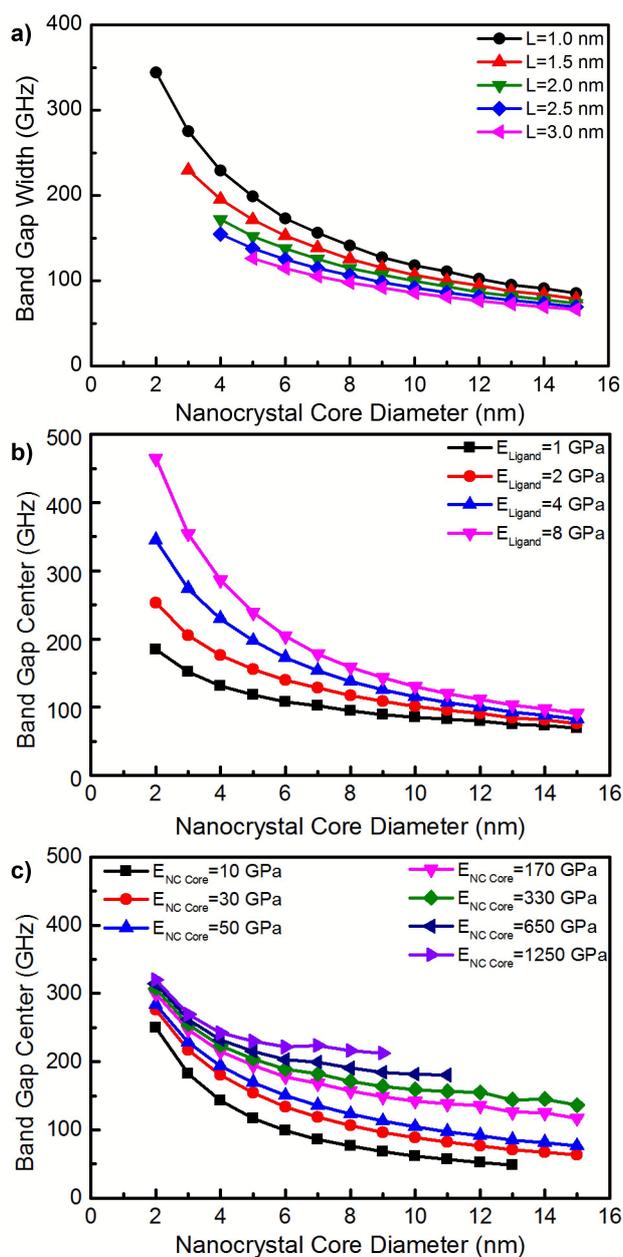


Figure 4. The effect of nanocrystal core diameter on the center frequency of the phononic band gap for: (a) varying interparticle distance, L ; (b) varying elastic modulus of the ligand matrix, E_{ligand} ; and (c) varying elastic modulus of the nanocrystal core, $E_{NC\ Core}$. Unless otherwise specified, L , E_{ligand} , and $E_{NC\ Core}$ are fixed at 1.5 nm, 2.6 GPa, and 54 GPa, respectively. An equivalent version of this figure shown as a function of nanocrystal core volume fraction can be found in Figure S4 of the Electronic Supplementary Information.

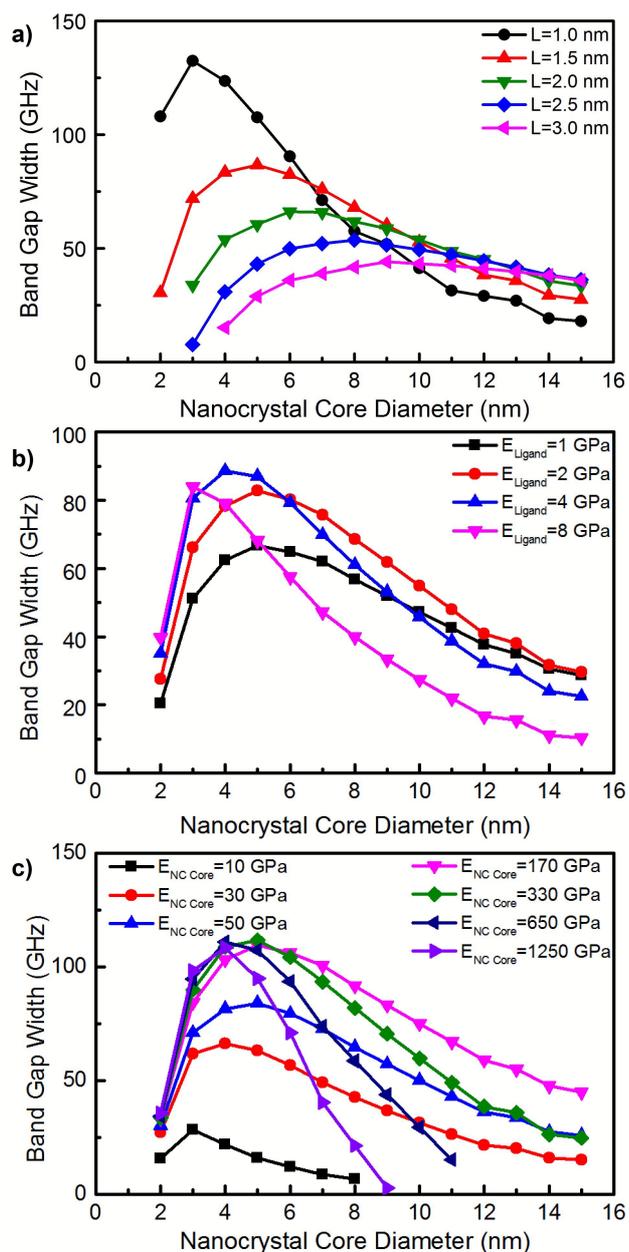
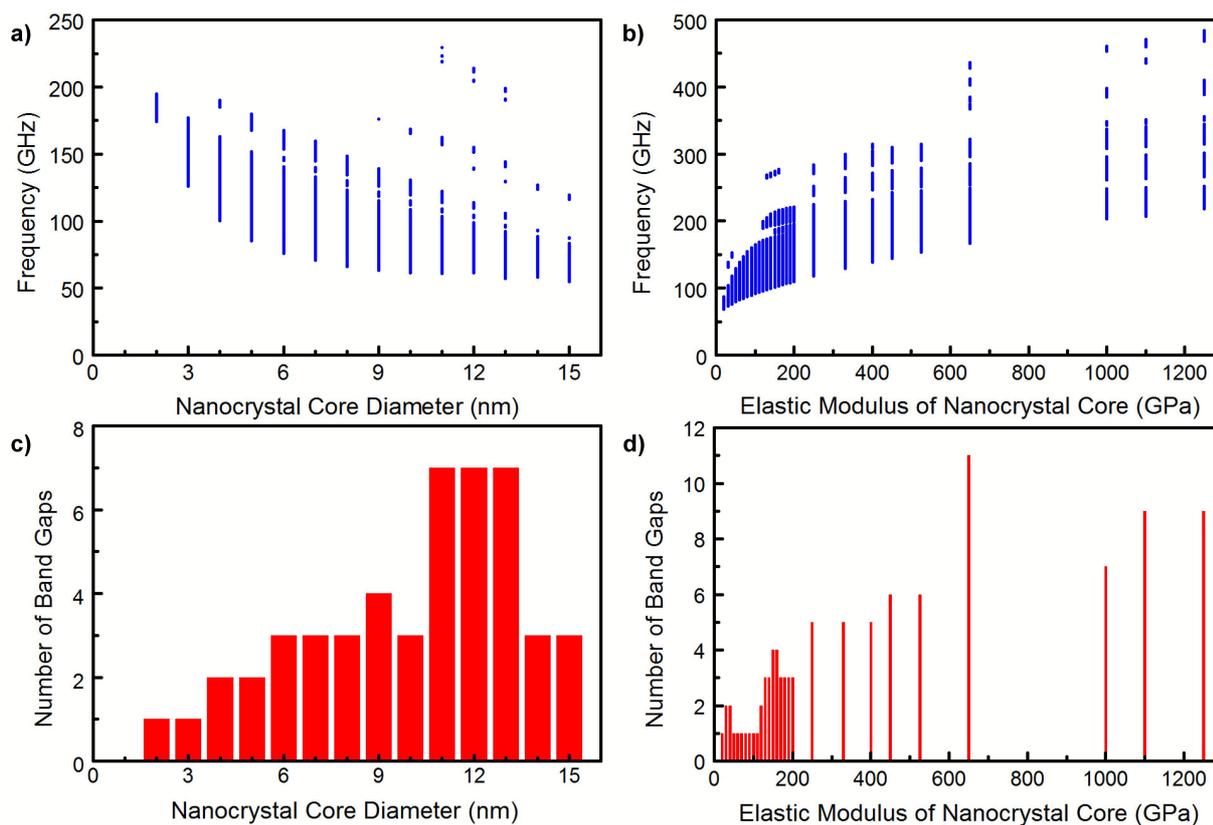


Figure 5. The effect of nanocrystal core diameter on the phononic band gap width for: (a) varying interparticle distance, L ; (b) varying elastic modulus of the ligand matrix, E_{Ligand} ; and (c) varying elastic modulus of the nanocrystal core, $E_{NC\ Core}$. Unless otherwise specified, L , E_{Ligand} , and $E_{NC\ Core}$ are fixed at 1.5 nm, 2.6 GPa, and 54 GPa, respectively. An equivalent version of this figure shown as a function of nanocrystal core volume fraction can be found in Figure S5 of the Electronic Supplementary Information.



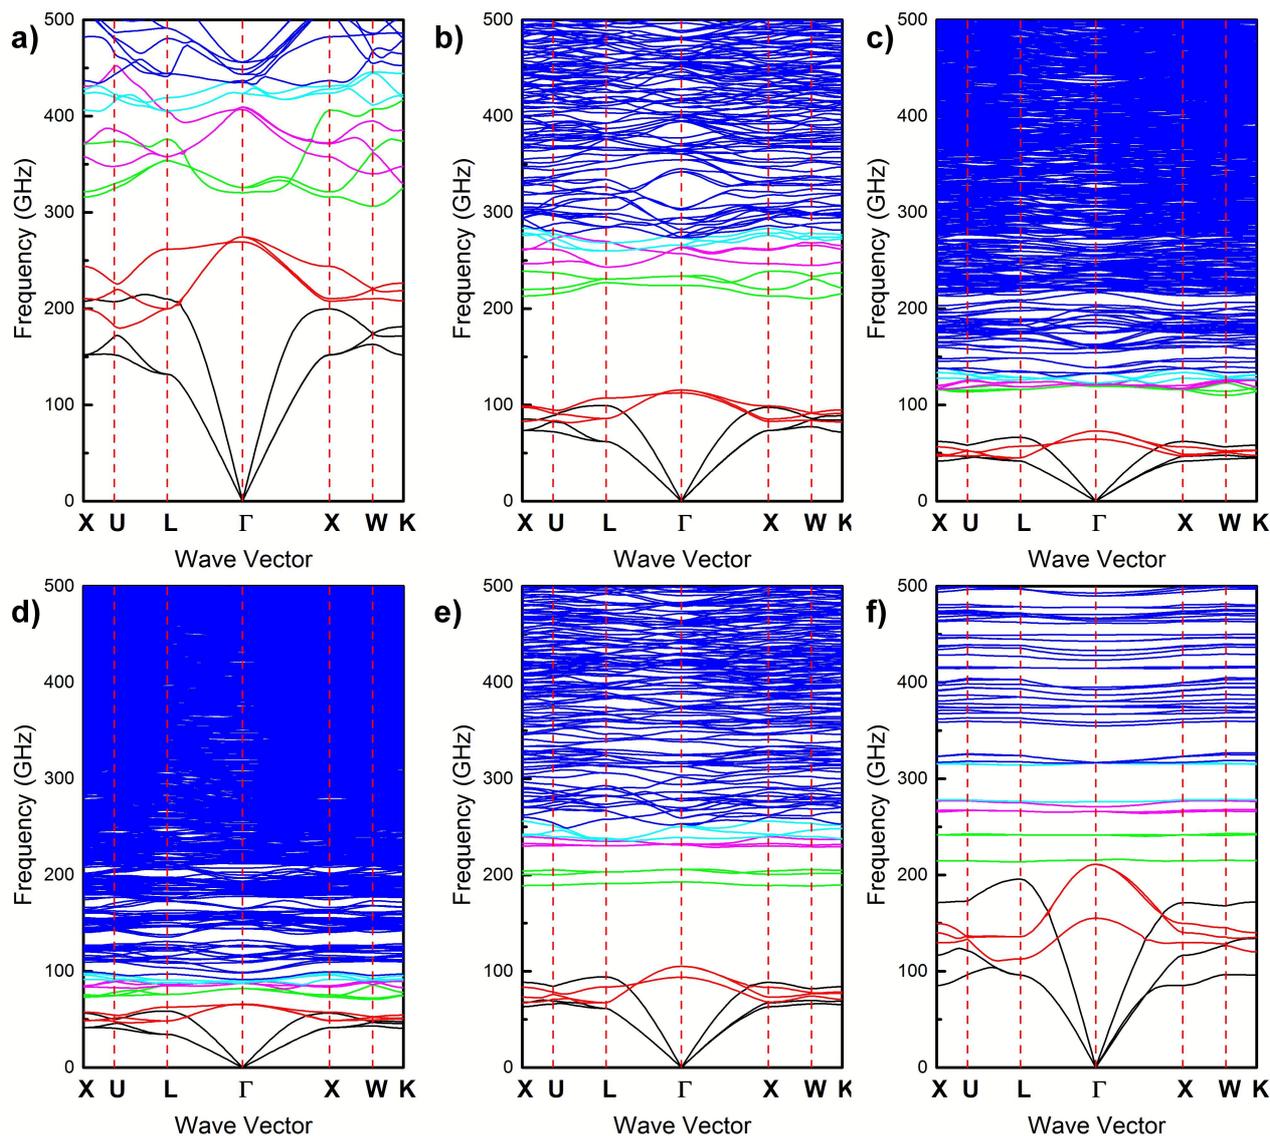


Figure 7. Phononic band diagrams for varying nanocrystal core diameters: (a) 2 nm, (b) 6 nm, and (c) 15 nm, and varying nanocrystal core elastic moduli: (d) 10 GPa, (e) 150 GPa, and (f) 1250 GPa. For diagrams (a) – (c), the interparticle distance, ligand modulus, and nanocrystal core modulus are 1.5 nm, 1 GPa, and 54 GPa, respectively. For diagrams (d) – (f), the interparticle distance, nanocrystal core diameter, and ligand modulus are 1.5 nm, 9 nm, and 2.6 GPa, respectively. To improve clarity, the first 5 sets of branches (i.e., 15 branches) are color-coded in each diagram. The three acoustic branches are black, the first set of optical branches are red, the second set of optical branches are green, and subsequent sets of optical branches are purple and cyan, respectively.

