



Cite this: *Polym. Chem.*, 2016, 7, 2087

## Enhanced catalytic activity of oxovanadium complexes in oxidative polymerization of diphenyl disulfide†

Fuyuki Aida,<sup>a,b</sup> Yohei Takatori,<sup>a</sup> Daichi Kiyokawa,<sup>a</sup> Kentaro Nagamatsu,<sup>a</sup> Kenichi Oyaizu<sup>\*a</sup> and Hiroyuki Nishide<sup>\*a</sup>

Oxygen-oxidative polymerization of diphenyl disulfide gives poly(1,4-phenylene sulfide) (PPS), catalyzed by a vanadyl complex and a protic acid. *N,N'*-Ethylenebis(salicylideneaminato)oxovanadium(IV) (VO(salen)) which has been reported to be catalytically inactive at ambient temperature because of the insufficient reactivity of its oxidized state, an oxovanadium(V) complex, for the oxidation of the monomer turned out to exhibit an excellent catalytic activity on raising the reaction temperature above 100 °C. The enhanced reactivity of VO(salen)-acid or bis(2,4-pentanedionato)oxovanadium(IV) (VO(acac)<sub>2</sub>)-acid catalytic systems at elevated temperatures gave insight into the catalytic mechanism where oxidation of the monomer with the oxovanadium(V) complex dominated the reactivity, which was also accelerated by a second redox shuttle molecule, such as quinones with a potential near that of the [VO(salen)]<sup>0/+</sup> couple.

Received 12th December 2015,  
Accepted 14th February 2016  
DOI: 10.1039/c5py01980j

www.rsc.org/polymers

### Introduction

In polymer synthesis, organic reaction of sulfur-containing molecules has been paid much attention, because of their unique properties. In addition to utilizing various kinds of sulfur-containing monomers represented by thiophenes, C–S bond formation is quite useful to yield polymers. Thiolates (RS<sup>−</sup>) as nucleophiles and sulfenyl cations (RS<sup>+</sup>) as electrophiles are used for this purpose. The nucleophilic reaction of RS<sup>−</sup> is typically represented by bis-hydrothiolation of thiols to alkynes to give thioacetals using calcium catalysts<sup>1</sup> and thia-Michael addition of RS<sup>−</sup> to cyclohexenone followed by Baeyer–Villiger oxidation and finally giving sulfone-containing polyesters *via* ring-opening polymerization.<sup>2</sup> Sulfonium electrophiles (RS<sup>+</sup>) have been employed under dehydrated conditions, such as the addition of electrochemically generated bis(arylthio)aryl sulfonium cation (ArS(ArSSAr)<sup>+</sup>) to olefins to give 1,2-bis(arylthio)-substituted compounds *via* the cationic chain reaction mechanism.<sup>3</sup> Palladium-catalyzed intermolecular C–H chalcogenation of arenes with disulfides or diselenides has also been reported.<sup>4</sup> Using phenylsulfenophthalimide as the PhS<sup>+</sup> source, a Brønsted acid-chiral binaphthyl ligand system catalyzed carbosulfenylation of olefins enantioselectively and

intramolecularly.<sup>5</sup> The sulfonium electrophile, derived from the condensation of methyl(4-phenylthio)phenyl sulfoxide, was also used for the synthesis of poly(methylsulfonio-1,4-phenylene-thio-1,4-phenylene trifluoromethanesulfonate).<sup>6a</sup> The condensation was applied in many kinds of polysulfonium syntheses including those for heteropolyacenes.<sup>6</sup> Recently, as represented by copper acetate–dimethyl sulfoxide (DMSO) promoted methylthiolation of arenes,<sup>7</sup> β-hydroxysulfide synthesis *via* air oxidative hydroxysulfurization<sup>8</sup> and dithioether synthesis from 1,3-dithianes *via* ring-opening and palladium catalyzed C–S bond formation have been reported.<sup>9</sup> Sulfur chemistry is thus one of the hot topics in current organic chemistry relevant to polymer synthesis.<sup>10</sup> However, catalytic systems to produce the synthetically useful sulfonium electrophiles have been limited to those used in our previous research on the oxygen-oxidative polymerization of diphenyl disulfide catalyzed by VO(acac)<sub>2</sub>.

Our research group has been focusing on the chemistry of the ArS(ArSSAr)<sup>+</sup> electrophile, especially its formation and reactivity by catalytic oxidation of the corresponding ArSSAr using a vanadyl catalyst.<sup>11</sup> The chemical structure of the sulfonium cation, having a three-membered sulfur ring, was determined by <sup>1</sup>H and <sup>13</sup>C NMR of bis(methylthio)methyl sulfonium<sup>11e</sup> and *in situ* Raman spectroscopy of ArS(ArSSAr)<sup>+</sup> (Ar = *p*-FC<sub>6</sub>H<sub>4</sub>).<sup>3c</sup> This kind of sulfonium cation was applied to poly(1,4-arylene sulfide) (PAS) synthesis, under oxidative conditions with a vanadyl catalyst and oxygen. In previous studies, it was reported that the bis(phenylthio)phenyl sulfonium (PhS(PhSSPh)<sup>+</sup>) ion was identified to be the active species of the

<sup>a</sup>Department of Applied Chemistry, Waseda University, Tokyo 169-8555, Japan.

E-mail: nishide@waseda.jp, oyaizu@waseda.jp

<sup>b</sup>JX Nippon Oil & Energy Corporation, Kanagawa, 231-0815, Japan

†Electronic supplementary information (ESI) available. See DOI: 10.1039/c5py01980j



oxygen-oxidative polymerization of PhSSPh, propagating the “PhS” unit *via* Friedel–Crafts (FC) type electrophilic aromatic substitution (Fig. 1).<sup>12</sup> Vanadyl complexes, such as VO(acac)<sub>2</sub> (acac<sup>−</sup> is the acetylacetonato ligand), V(acac)<sub>3</sub>, bis(1-phenyl-2,4-pentanedionato)oxovanadium (VO(dbm)<sub>2</sub>), and (*meso*-tetraphenylporphyrinato)oxovanadium (VO(TPP)) catalyzed the oxygen-oxidative polymerization.<sup>11d</sup> However, the inherent lability of the β-diketonato ligand such as acac<sup>−</sup> has impeded to unravel the catalytic mechanism. The lack of the catalytic activity of VO(salen) (where salen<sup>2−</sup> is an inert four-coordinate *N,N'*-ethylene-bis(salicylideneaminato) ligand) with a more negative redox potential suggested that the overall activity of the catalyst was dominated by the oxidation of the monomer with the catalyst (Fig. 1). We report here that the VO(salen)-catalyzed oxygen-oxidative polymerization of PhSSPh proceeds at elevated temperatures, which revealed that the complex was sufficiently robust as a result of the inertness of the ligand and yet the reactivity of VO(salen) is significantly enhanced.

H<sub>2</sub>salen and its derivatives are quite stable compounds and are useful as inert tetradentate ligands for various metal ions. Ruthenium(III)-, iron(II), copper(II)- and oxovanadium(IV)-salen complexes are typically classified into highly stable and robust complexes, which can be used as catalysts for oxidative reactions with peroxides and other oxidants.<sup>13</sup> Oxygen or air is the ultimate oxidant in biological systems and the most economical reagent for oxidation in organic synthesis. To reduce oxygen, four-electron and four-proton transfers are essential according to O<sub>2</sub> + 4H<sup>+</sup> + 4e<sup>−</sup> → 2H<sub>2</sub>O. The two-electron and two-proton transfers give rise to a hydroxide according to O<sub>2</sub> + 2H<sup>+</sup> + 2e<sup>−</sup> → H<sub>2</sub>O<sub>2</sub> which is often undesirable in the respiratory systems and organic synthesis. So far, many kinds of organometallic complexes have been reported, showing various types of the multi-electron transfer processes.<sup>14,15</sup> The above mentioned oxygen-oxidative polymerization of PhSSPh is one of the four-electron-transfer preferred reactions to give H<sub>2</sub>O as the byproduct, because the hydroxide instantly oxygenates, rather than oxidating the disulfide to yield the undesired sulfoxides and sulfones.<sup>11,12,15,16</sup> Although VO(salen) did not show the catalytic activity for polymerization under ambient conditions, the enhanced chemical robustness of VO(salen) and its oxidized [VO(salen)]<sup>+</sup>, suggested by the electrochemically almost totally reversible nature of the couple which is in sharp contrast to the quasi-reversible response obtained for [VO(acac)<sub>2</sub>]<sup>0/+</sup>, clearly indicated the possibility of exploring more severe conditions with VO(salen) to undergo the four-electron transfer reaction.<sup>11d,16b</sup>

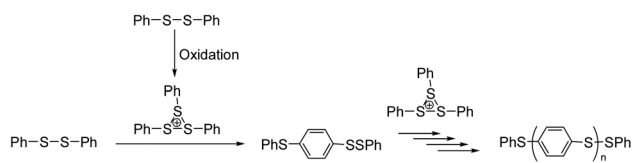


Fig. 1 Oxidative polymerization of PhSSPh *via* FC electrophilic reaction of the sulfonium cation.

The mediated oxidation of PhSSPh catalyzed by the vanadyl complexes requires that the redox potentials of the vanadyl complexes be located in-between the potentials for the oxidation of PhSSPh near 1.7 V vs. Ag/AgCl and that for the four-electron reduction of oxygen near 0.5 V at room temperature. We previously reported that the potential range of 0.8–1.5 V for the vanadyl complex was appropriate to catalyze the polymerization.<sup>11d</sup> VO(acac)<sub>2</sub> catalyzed the polymerization, because its redox potential was estimated to be near 1.1 V.<sup>11b</sup> The lack of the catalytic activity of VO(salen) was ascribed to the negative redox potential for the [VO(salen)]<sup>0/+</sup> couple at a half-wave potential of  $E_{1/2} = 0.5$  V.<sup>11d</sup> However, one could assume that the reactivity of those of the less oxidizing vanadyl complexes should be enhanced at elevated temperatures,<sup>17</sup> according to Nernst's equation which suggests that the redox potential shifts positively with temperature. We report here our successful attempt to enhance the catalytic activity at moderately elevated temperatures by applying a pressurized condition (*ca.* 0.45 MPa) to partially maintain the oxygen concentration. Another effective means to enhance the catalytic activity is to combine an additional redox cycle with the oxovanadium(IV/V) couple. The effect of applying such multiple redox cycles formed in-between the monomer and oxygen has been examined in our previous work on the polymerization of bis(3,5-dimethylphenyl)disulfide using VO(acac)<sub>2</sub> and 2,3-dichloro-5,6-dicyano-*p*-benzoquinone (DDQ) in the presence of trifluoroacetic acid (CF<sub>3</sub>CO<sub>2</sub>H) under ambient conditions with (CF<sub>3</sub>CO)<sub>2</sub>O in a halogenated hydrocarbon as a solvent.<sup>16a</sup> This method of enhancing the catalytic activity proved to have an inherent advantage over just raising the reaction temperature, because of the capability of undergoing the polymerization under atmospheric pressure. In search of quinones that match the conditions to undergo the polymerization of the disulfide at moderately elevated temperatures, we have found that 2,3,5,6-tetrabromo-*p*-benzoquinone (bromanil) significantly enhances the catalytic activity of the vanadyl complexes to produce polymers with larger molecular weights.

## Experimental section

### Materials

PhSSPh, VO(acac)<sub>2</sub>, bromanil, TrB(C<sub>6</sub>F<sub>5</sub>)<sub>4</sub> (Tr<sup>+</sup> = the triphenylmethylinium cation), TfOH, and CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H were obtained from Tokyo Kasei Co., and were used without further purification. VO(salen) was prepared as previously reported.<sup>18</sup>

### Measurements

Molecular weight measurements were done by gel permeation chromatography using an AGILENT PL-220 and 1-chloronaphthalene as the eluent (1 ml min<sup>−1</sup>) maintained at 210 °C. Calibration was done with polystyrene standards. Melting points were recorded using a differential scanning calorimeter (DSC, Seiko Instruments Inc. DSC-220), by scanning from 20 to 310 °C at a rate of 20 °C min<sup>−1</sup> with alpha-alumina as the reference. Cyclic voltammetry was performed in 0.1 M solution of



tetrabutylammonium tetrafluoroborate (TBABF<sub>4</sub>) in 1,2-dichloroethane with Pt working electrodes. The electrode potential of the working electrode was set *versus* the commercial Ag/AgCl reference electrode, and was scanned at a speed of 100 mV s<sup>-1</sup> using an ALS/CH Instruments Electrochemical Analyzer (Model 660Dx) at -10, 20, and 70 °C. All potentials are shown with respect to this reference electrode.

### General procedure of oxygen-oxidative polymerization

To a 10 ml flask, 5 mmol of PhSSPh, vanadyl compound, acid or borate compound (CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H or TrB(C<sub>6</sub>F<sub>5</sub>)<sub>4</sub>), and bromanil were introduced. The mixture was heated and stirred under oxygen flow for 20–80 h. After cooling down to room temperature, the reaction mixture was dispersed into 50 ml of CH<sub>2</sub>Cl<sub>2</sub> and the dispersion was poured into 300 ml of MeOH–HCl mixture (MeOH/HCl = 95/5, in v/v). The precipitation was collected with a glass filter. The solid was washed with MeOH and H<sub>2</sub>O, and dried under vacuum. The purified polymer yields, melting points and molecular weights were determined according to the methods described above. See the ESI† for experimental details.

### Procedure of pressurized oxygen-oxidative polymerization

To a 50 ml autoclave with a Teflon® inner tube, 31 mmol of PhSSPh, 1 mol% of VO(salen) and 1 mol% of 1,1,2,2-tetrafluoroethanesulfonic acid were introduced. The mixture was heated and stirred for 20 hours at 160 °C under discontinuously pressurized oxygen (depressurized to ambient pressure and pressurized to 0.45 MPa every 1 h). After the reaction, oxygen was depressurized and purged with nitrogen. Then the autoclave was cooled down to room temperature. The reaction mixture was dispersed into 50 ml of CH<sub>2</sub>Cl<sub>2</sub> and the dispersion was poured into 300 ml of MeOH–HCl mixture (MeOH/HCl = 95/5, in v/v). The precipitation was collected with a glass filter. The solid was washed with MeOH and H<sub>2</sub>O, and dried under vacuum to give purified PPS in 82% yield. Melting points and molecular weights were determined according to the methods described above.

## Results and discussion

### Oxygen-oxidative polymerization of PhSSPh catalysed by VO(salen) at elevated temperatures

Cyclic voltammograms of VO(salen) were recorded at -10, 20, and 70 °C, which revealed the redox potentials ( $E_{1/2}$ ) at 0.44, 0.47, and 0.56 V, respectively. Assuming a linearity of the formal potential with temperature,  $E_{1/2}$  was extrapolated to be 0.60, 0.64, and 0.69 V at 100, 130, and 160 °C, respectively. The positive shift in the redox potential that came into the region of the suitable range for catalysis suggested that the oxygen-oxidative polymerization should proceed above 100 °C when VO(salen) is used as the catalyst (Fig. 2).

Table 1 shows the results of the oxygen-oxidative polymerization of the disulfide with the VO(salen) catalyst, which was inactive at room temperature (entry 1) but gained activity at

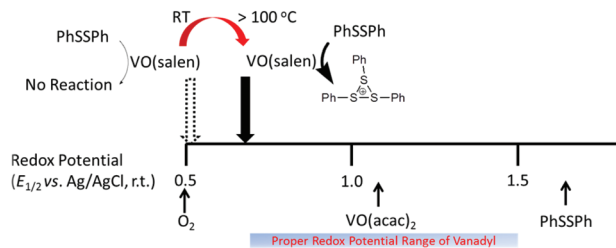


Fig. 2 Potential diagram of the catalyst at elevated temperatures.

100 °C (entry 2). Comparison between entries 2 and 4 suggested that higher reaction temperatures led to higher yields and melting points ( $T_m$ ) of the products. Also, comparison between entries 3 and 6 indicated that the higher reaction temperatures resulted in higher yields and  $T_m$  of the products even in a shorter reaction time. Both the strong acid and the borate gave rise to the polymerization activity with VO(salen) (entries 4 and 5). Considering that the reactivity was limited by the equilibrated oxygen concentration which should be lowered at elevated temperatures, we adopted a pressurized condition (entry 7) to further enhance the reactivity. As expected, a higher molecular weight and  $T_m$  for the obtained PPS was accomplished in an even shorter time of the polymerization, compared with the results in entry 6. These results demonstrated the first catalysis of the oxidative polymerization of the disulfide by VO(salen) which has so far been regarded as inactive, suggesting that the electrochemical reversibility persisted at elevated temperatures as a result of the inertness of the salen<sup>2-</sup> ligand to give rise to the positive shift of the formal potential for the [VO(salen)]<sup>0/+</sup> couple. The polymer obtained by this method was generally linear without branching or crosslinking as evidenced by the presence of only two carbon signals in the CP-MAS spectrum corresponding to the structural symmetry and the IR peak at 820 cm<sup>-1</sup> ascribed to the C–H out-of-plane vibration of adjacent two hydrogens in the 1,4-phenylene unit,<sup>10,17,19</sup> suggesting the highly selective catalysis by VO(salen) (see the ESI†). The present study is the first achievement of catalytic activity of VO(salen) for the polymerization of the disulfide, while the catalytic mechanism of the vanadyl catalyst has so far been determined with the complexes bearing the inert salen<sup>2-</sup> ligand and yet the catalytic activity has so far been obtained only for those having labile acac<sup>-</sup> and related ligands.<sup>11d</sup> The results clearly demonstrated that the catalysis was accomplished by the incorporation of the multi-electron transfer process established for VO(salen).<sup>16e</sup>

### Bromanil-assisted catalysis of oxygen-oxidative polymerization of PhSSPh by vanadyl complexes

Under ambient temperature conditions, quinones such as DDQ and bromanil are known to enhance the reactivity of the VO(acac)<sub>2</sub>-acid catalytic system for the oxygen-oxidative polymerization of PhSSPh or diaryl disulfide.<sup>16a</sup> Assuming that the quinones should also enhance the reactivity of VO(salen), we turned to examine the catalysis by VO(salen) under



**Table 1** Oxygen-oxidative polymerization of PhSSPh with VO(salen)<sup>a</sup>

Entry	Acid or borate (mol%)	Temp. (°C)	Time (h)	Yield (%)	<i>T</i> <sub>m</sub> <sup>b</sup> (°C)	<i>M</i> <sub>n</sub> <sup>c</sup>	<i>M</i> <sub>w</sub> <sup>c</sup>
1 <sup>d</sup>	TfOH (10)	RT	40	0			
2	TrB(C <sub>6</sub> F <sub>5</sub> ) <sub>4</sub> (10)	100	20	52	149		
3 <sup>e</sup>	CHF <sub>2</sub> CF <sub>2</sub> SO <sub>3</sub> H (1)	130	80	70	163	1200	1600
4	TrB(C <sub>6</sub> F <sub>5</sub> ) <sub>4</sub> (10)	160	20	69	254	880	1800
5	CHF <sub>2</sub> CF <sub>2</sub> SO <sub>3</sub> H (10)	160	20	69	198	1500	3400
6 <sup>e</sup>	CHF <sub>2</sub> CF <sub>2</sub> SO <sub>3</sub> H (1)	160	40	82	175	1100	1500
7 <sup>f</sup>	CHF <sub>2</sub> CF <sub>2</sub> SO <sub>3</sub> H (1)	160	20	82	205	1800	4400

<sup>a</sup> 5 mol% of VO(salen) was used. <sup>b</sup> Determined by DSC. <sup>c</sup> Measured by high temperature GPC. <sup>d</sup> Data from ref. 3a. <sup>e</sup> 1 mol% of VO(salen) was used. <sup>f</sup> 1 mol% of VO(salen) was used and the oxygen pressure was 0.45 MPa.

moderately elevated conditions in the presence of the quinones. These quinones are good chemical oxidants that undergo oxidative polymerization of PhSSPh when an equimolar amount of the oxidant is used.<sup>11a</sup> A catalytic amount of quinones gave only a trace amount of the polymerized product as typically shown for the case of 2.5 mol% bromanil and 5 mol% CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H with respect to the monomer after 4 h of the reaction (entry 1 in Table 2). It might be suggested that catalysis by bromanil was accomplished by placing the potential of bromanil near to an oxovanadium(IV/V) couple such as [VO(salen)]<sup>0/+</sup>. An interesting aspect of the bromanil was found for the combination with VO(acac)<sub>2</sub> or VO(salen) at moderately elevated temperatures, which demonstrated the catalytic activity even higher than those found for the conventional catalysis by VO(acac)<sub>2</sub> or VO(salen). When 2.5 mol% VO(acac)<sub>2</sub> was combined with the bromanil-acid system, the polymerization proceeded rapidly to give PPS in a 51% yield within 1 h (entry 2). Under the same conditions as in entry 2, a higher molecular-weight PPS was obtained in 82% yield after 4 h (entry 3). In the case of the conventional oxidative polymerization without bromanil, 5 mol% VO(acac)<sub>2</sub> and CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H gave PPS in yields of only 22% after 1 h (entry 4) and 74% after 4 h (entry 5), which were much lower than those for the entries 2 and 3. Strong acids or borate compounds, such as CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H and TrB(C<sub>6</sub>F<sub>5</sub>)<sub>4</sub>, were essential to activate the vanadyl compounds.<sup>19</sup> Even for the oxidative polymerization with quinones, strong acids were found to be essential for stabilizing the key intermediate, the sulfonium cation (PhS(PhSSPh)<sup>+</sup>).<sup>19</sup> In the case of utilizing a VO(salen)-acid catalytic

system, bromanil similarly accelerated the oxidative polymerization (entries 6 and 7). These results gave insight into the nature of the catalysis which was dominated by the oxidation of the monomer and much improved by placing a second redox couple to enhance the overall reactivity under moderately elevated temperature conditions to yield PPS with a higher molecular weight than those with the conventional catalyst system. It was reported that the redox potentials of quinones were positively shifted under acidic conditions.<sup>20</sup> Actually, the redox potential of bromanil (*E*<sub>1/2</sub> = -0.71 and 0.11 V vs. Ag/AgCl, r.t.) was shifted to 0.1 and 0.5 V to show the irreversible reduction to yield the protonated product under acidified conditions (see the ESI<sup>†</sup>). During the polymerization, the anionic species, such as the reduced forms of the quinones or the conjugated bases of strong acids, were reported to stabilize the cationic species, typically the sulfonium cations.<sup>19</sup> Bromanil turns out to be an anionic species by reduction, so the reduced bromanil might be able to form complexes with the cationic vanadyl compounds. It may be suggested that the effective enhanced catalytic systems of the vanadyl-acid-bromanil triad was ascribed to the re-oxidation of the possibly newly formed complex between the vanadyl catalyst and the reduced bromanil. Further investigation of the mechanism is the topic of our continuous research.

## Conclusions

The VO(salen)-catalyzed oxygen-oxidative polymerization of PhSSPh was successfully established above 100 °C. Pressurized oxygen further accelerated the oxidative polymerization and gave higher molecular weight products in high yield. The results demonstrated that catalysis was dominated by the oxidation of the monomer rather than re-oxidation of the catalyst by oxygen, which was also supported by the enhanced reactivity of the vanadyl catalyst with bromanil. Further modification of the catalyst with a view to yield a higher molecular weight PPS is the topic of our continuous research.

## Acknowledgements

This work was partially supported by Grants-in-Aid for Scientific Research (No. 24225003, 25288056, 26620108) from MEXT, Japan.

**Table 2** Oxidative polymerization with the vanadyl-oxidant system<sup>a</sup>

Entry	Vanadyl (mol%)	Bromanil (mol%)	Time (h)	Yield (%)	<i>M</i> <sub>n</sub> <sup>b</sup>	<i>M</i> <sub>w</sub> <sup>b</sup>
1 <sup>c</sup>	0	2.5	4	Trace		
2	2.5 <sup>d</sup>	2.5	1	51	900	1100
3	2.5 <sup>d</sup>	2.5	4	82	1600	2400
4	5 <sup>d</sup>	0	1	22	680	850
5	5 <sup>d</sup>	0	4	74	1300	1600
6	2.5 <sup>e</sup>	2.5	4	56	960	1300
7	5 <sup>e</sup>	0	4	24		

<sup>a</sup> [CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H]/[vanadyl] = 2, oxygen atmosphere, polymerized at 160 °C. <sup>b</sup> Determined by high temperature GPC. <sup>c</sup> 5 mol% of CHF<sub>2</sub>CF<sub>2</sub>SO<sub>3</sub>H was used. <sup>d</sup> VO(acac)<sub>2</sub> was used. <sup>e</sup> VO(salen) was used.



## Notes and references

- 1 M. Hut'ka, T. Tsubogo and S. Kobayashi, *Organometallics*, 2014, **33**, 5626.
- 2 M. Winkler, Y. Raupp, L. Koehl, H. Wagner and M. Meier, *Macromolecules*, 2014, **47**, 2842.
- 3 (a) K. Matsumoto, T. Sanada, H. Shimazaki, K. Shimada, S. Hagiwara, S. Fujie, Y. Ashikari, S. Suga, S. Kashimura and J. Yoshida, *Asian J. Org. Chem.*, 2013, **2**, 325; (b) K. Matsumoto, S. Fujie, S. Suga, T. Nokami and J. Yoshida, *Chem. Commun.*, 2009, 5448; (c) K. Matsumoto, Y. Miyamoto, K. Shimada, Y. Morisawa, H. Zipse, S. Suga, J. Yoshida, S. Kashimura and T. Wakabayashi, *Chem. Commun.*, 2015, **51**, 13106.
- 4 R. Qiu, V. P. Reddy, T. Iwasaki and N. Kambe, *J. Org. Chem.*, 2015, **80**, 367.
- 5 S. Denmark and H. Chi, *J. Am. Chem. Soc.*, 2014, **136**, 3655.
- 6 (a) E. Tsuchida, K. Yamamoto and E. Shouji, *Macromolecules*, 1993, **26**, 7389; (b) K. Miyatake, K. Oyaizu, Y. Nishimura and E. Tsuchida, *Macromolecules*, 2001, **34**, 1172; (c) K. Oyaizu, T. Mikami, F. Mitsunashi and E. Tsuchida, *Macromolecules*, 2002, **35**, 67; (d) K. Oyaizu, F. Mitsunashi and E. Tsuchida, *Macromol. Chem. Phys.*, 2002, **203**, 1328; (e) K. Oyaizu, T. Iwasaki, Y. Tsukahara and E. Tsuchida, *Macromolecules*, 2004, **37**, 1257; (f) K. Oyaizu, T. Mikami and E. Tsuchida, *Macromolecules*, 2004, **37**, 2325.
- 7 P. Sharma, S. Rohilla and N. Jain, *J. Org. Chem.*, 2015, **80**, 4116.
- 8 S. Zhou, X. Pan, Z. Zhou, A. Shoberu and J. Zou, *J. Org. Chem.*, 2015, **80**, 3682.
- 9 N. Abidi and J. Schmink, *J. Org. Chem.*, 2015, **80**, 4123.
- 10 F. Aida and K. Oyaizu, *Chem. Lett.*, 2016, **45**, 201.
- 11 (a) E. Tsuchida, K. Yamamoto, M. Jikei, E. Shouji and H. Nishide, *J. Macromol. Sci., Part A: Pure Appl. Chem.*, 1991, **28**, 1285; (b) K. Yamamoto, M. Jikei, J. Katoh, H. Nishide and E. Tsuchida, *Macromolecules*, 1992, **25**, 2698; (c) E. Shouji, K. Yamamoto, J. Katoh, H. Nishide and E. Tsuchida, *Polym. Adv. Technol.*, 1991, **2**, 149; (d) K. Yamamoto, E. Tsuchida, H. Nishide, M. Jikei and K. Oyaizu, *Macromolecules*, 1993, **26**, 3432; (e) E. Tsuchida, K. Yamamoto and E. Shouji, *J. Macromol. Sci., Part A: Pure Appl. Chem.*, 1994, **31**, 1579.
- 12 E. Tsuchida and K. Oyaizu, *Bull. Chem. Soc. Jpn.*, 2003, **76**, 15.
- 13 (a) Y. Fukunaga, T. Uchida, Y. Ito, K. Matsumoto and T. Katsuki, *Org. Lett.*, 2012, **12**, 4658; (b) S. Koya, Y. Nishioka, H. Mizoguchi, T. Uchida and T. Katsuki, *Angew. Chem., Int. Ed.*, 2012, **51**, 8243; (c) H. Mizoguchi, T. Uchida and T. Katsuki, *Angew. Chem., Int. Ed.*, 2014, **53**, 3178; (d) Y. Nishioka, T. Uchida and T. Katsuki, *Angew. Chem., Int. Ed.*, 2013, **52**, 1739; (e) K. Matsumoto, H. Egami, T. Oguma and T. Katsuki, *Chem. Commun.*, 2012, **48**, 5823; (f) T. Oguma and T. Katsuki, *Chem. Commun.*, 2014, **50**, 5053; (g) M. Nikoorazm, A. G-Choghamarani, F. Ghorbani, H. Mahdavi and Z. Karamshahi, *J. Porous Mater.*, 2015, **22**, 261; (h) P. Du, H. Li, Y. Wang, J. Cheng and X. Wan, *Org. Lett.*, 2014, **16**, 6350; (i) A. Mathavan, A. Ramdass and S. Rajagopal, *Transition Met. Chem.*, 2015, **40**, 355; (j) A. Berkessel, T. Günther, T. Wang and J.-M. Neudröft, *Angew. Chem., Int. Ed.*, 2013, **52**, 8467.
- 14 (a) S. Fukuzumi, L. Tahsini, Y. M. Lee, K. Ohkubo, W. Nam and K. D. Karlin, *J. Am. Chem. Soc.*, 2012, **134**, 7025; (b) S. Kakuda, R. L. Peterson, K. Ohkubo, K. D. Karlin and S. Fukuzumi, *J. Am. Chem. Soc.*, 2013, **135**, 6513; (c) J. Y. Lee, R. L. Peterson, K. Ohkubo, I. Garcia-Bosh, R. A. Himes, J. Woertink, C. D. Moore, E. I. Solomon, S. Fukuzumi and K. D. Karlin, *J. Am. Chem. Soc.*, 2014, **136**, 9925; (d) A. Yokoyama, J. E. Han, K. D. Karlin and W. Nam, *Chem. Commun.*, 2014, **50**, 1742; (e) I. Garcia-Bosh, S. M. Adam, A. W. Schaefer, E. I. Solomon and K. D. Karlin, *J. Am. Chem. Soc.*, 2015, **137**, 1032; (f) S. Kim, J. Y. Lee, R. E. Cowley, J. W. Ginsbach, M. A. Siegler, E. I. Solomon and K. D. Karlin, *J. Am. Chem. Soc.*, 2015, **137**, 2769; (g) A. Hay, *US Patent*, 3306874, 1967.
- 15 (a) K. Oyaizu, Y. Kumaki, K. Saito and E. Tsuchida, *Macromolecules*, 2000, **33**, 5766; (b) K. Oyaizu, K. Saito and E. Tsuchida, *Chem. Lett.*, 2000, 1318; (c) K. Saito, T. Masuyama, K. Oyaizu and H. Nishide, *Chem. – Eur. J.*, 2003, **9**, 4240; (d) E. Tsuchida, K. Yamamoto and K. Oyaizu, *Multi-electron Transfer and Catalytic Mechanisms in Oxidative Polymerization*, Marcel Dekker, New York, 1999, p. 535.
- 16 (a) K. Yamamoto, M. Jikei, K. Oyaizu, F. Suzuki, H. Nishide and E. Tsuchida, *Bull. Chem. Soc. Jpn.*, 1994, **67**, 251; (b) K. Yamamoto, K. Oyaizu and E. Tsuchida, *Polym. Adv. Technol.*, 1995, **6**, 155; (c) K. Oyaizu, K. Yamamoto, K. Yoneda and E. Tsuchida, *Inorg. Chem.*, 1996, **35**, 6634; (d) E. Tsuchida, K. Yamamoto, K. Oyaizu, N. Iwasaki and F. Anson, *Inorg. Chem.*, 1994, **33**, 1056; (e) E. Tsuchida and K. Oyaizu, *Coord. Chem. Rev.*, 2003, **237**, 213; (f) E. Tsuchida, K. Yamamoto and K. Oyaizu, *Molecular Conversion Based on Multi-electron Transfer System*, Kodansha, Tokyo, 1995, p. 41; (g) E. Tsuchida, K. Yamamoto and K. Oyaizu, *Multi-electron Transfer Process of a Vanadium Dinuclear Complex for Molecular Conversions*, Plenum Press, New York, 1996, p. 139; (h) M. Jikei, J. Katoh, N. Sato, K. Yamamoto, H. Nishide and E. Tsuchida, *Bull. Chem. Soc. Jpn.*, 1992, **65**, 2029.
- 17 F. Aida, Y. Takatori, D. Kiyokawa, K. Nagamatsu, H. Nishide and K. Oyaizu, *Chem. Lett.*, 2015, **44**, 767.
- 18 J. A. Bonadies and C. J. Carrano, *J. Am. Chem. Soc.*, 1986, **108**, 4088.
- 19 F. Aida, S. Yamaguchi, Y. Takatori, K. Nagamatsu, D. Kiyokawa, K. Oyaizu and H. Nishide, *Macromol. Chem. Phys.*, 2015, **216**, 1850.
- 20 K. Oyaizu, N. Iwasaki, K. Yamamoto, H. Nishide and E. Tsuchida, *Bull. Chem. Soc. Jpn.*, 1994, **67**, 1456.

