

Cite this: *Energy Adv.*, 2024,
3, 30Received 13th October 2023,
Accepted 6th December 2023

DOI: 10.1039/d3ya00506b

rsc.li/energy-advances

A review on the advancements of graphitic carbon nitride-based photoelectrodes for photoelectrochemical water splitting

Merin Joseph, ^a Mohit Kumar, ^{cd} Suja Haridas, ^{ab}
Challapalli Subrahmanyam ^{bc} and Sebastian Nybin Remello ^{ab}

Photoelectrochemical water splitting has been envisaged as a promising green technology for efficient solar-to-fuel conversion. Graphitic carbon nitride (g-C₃N₄) demands prime focus among the emerging class of potential 2D materials for energy harvesting and storage on account of its high chemical/thermal stability and metal-free nature. The unique characteristics of the material enable its application as both a photocathode and photoanode. However, the low photocurrent density of pristine g-C₃N₄ curbs its possible commercial application. Considerable attempts to modify the electrodes via nanostructuring, heteroatom doping, heterojunction formation, and other methods are in progress. The current review offers insights into the potential and limitations of g-C₃N₄ as a photoanodic/cathodic material.

^a Department of Applied Chemistry, Cochin University of Science and Technology, Kochi, Kerala, 682022, India. E-mail: sujaharidas@cusat.ac.in

^b Inter University Centre for Nanomaterials and Devices, Cochin University of Science and Technology, Kochi, Kerala, India

^c Department of Chemistry, Indian Institute of Technology Hyderabad, Hyderabad, Telangana, 502285, India. E-mail: csubbu@iith.ac.in

^d Department of Chemistry and Biochemistry, School of Science Computing and Engineering, Swinburne University of Technology, Hawthorn, VIC-3122, Australia

1. Introduction

The rapidly growing energy demands have challenged the scientific society to come up with clean, renewable, and sustainable energy sources. However, clean renewable resources, such as solar, tidal, wind, and geothermal energy, have their own sets of limitations that hamper the replacement of the current fossil fuel-based non-renewable resources.¹ In this scenario, solar energy utilisation remains the most promising

**Merin Joseph**

Merin Joseph obtained her postgraduate degree in Chemistry from St. George's College, Mahatma Gandhi University, Kerala. Since July 2018, she has been a PhD student under the guidance of Dr Suja Haridas and the co-guidance of Dr Sebastian Nybin Remello in the Department of Applied Chemistry, Cochin University of Science and Technology. Her research focuses on the energy harvesting and environmental remediation based on graphitic carbon nitride hybrids.

**Mohit Kumar**

Mohit Kumar studied chemistry at the Indian Institute of Technology Hyderabad, India, where he obtained his postgraduate degree in Chemistry. Since May 2020, he has been a joint PhD student in the IITH-SUT joint doctoral programme under the guidance of Challapalli Subrahmanyam in the Department of Chemistry at the Indian Institute of Technology Hyderabad, TN, India, and the Chenghua Sun, School of Science, Engineering and Technology, Swinburne University of Technology, VIC, Australia. His research focuses on the development of novel Cu-based semiconducting photocathode configurations for solar water splitting.



approach to provide a sustainable solution to the energy crisis. Despite the abundant and inexhaustible solar energy incident on the earth's surface, the average utilisation remains meagre. The core requirement for solar energy utilisation is the mild conditions for the operational feasibility of reactions allowing for the fine-tuning of the selectivity.^{2,3} In conjunction with energy generation, energy storage is also of crucial significance, with electrochemical and chemical energy storage^{4,5} being equally explored in this domain. Efficient conversion of solar energy into chemical energy is as momentous and challenging as direct solar-to-electric conversion. Hydrogen is regarded as a potential clean fuel with zero carbon emission for the future, and sustainable H₂ generation demands prime priority. Of several available technologies for H₂ production, photoelectrochemical (PEC) water splitting has gained popularity owing to its relative simplicity and environmental benignity.^{1-3,6-9} In comparison with photocatalytic water splitting, PEC benefits from the generation of H₂ and O₂ over separate electrodes, avoiding gas mixing and back reactions. The external bias applied in PEC significantly allows for charge separation and migration, achieving high efficiency as compared to

photocatalytic water splitting. Photoelectrocatalysis has been applied in chemical synthesis and nitrogen reduction in addition to water splitting.^{10,11}

After the initial design of PEC water splitting by Fujishima and Honda,¹² the process has received much attention in the realm of solar energy conversion and storage revolution.¹³ A typical process in a PEC cell involves the light-assisted generation of voltage by photoactive semiconducting electrodes and the mobilization of charge carriers to bring forth water splitting. Efficient PEC water splitting entails materials complying with various criteria, including suitable band edge positions, an appreciable absorption of the solar spectrum, effective charge separation, high hydrolytic stability and photostability, and cost-effectiveness.^{1-3,6,13,14} Numerous semiconductor materials have been employed for efficient PEC water splitting.¹⁵⁻²⁶ However, due to the complex electrode kinetics, fast exciton recombination, large over potential, and photostability of materials, achievable solar-to-hydrogen conversion efficiencies (STH) remain too low, thus limiting the commercialisation of PEC water splitting.

Graphitic carbon nitride (g-C₃N₄), a metal-free polymeric semiconductor material, has aroused global interest as a multifunctional material for energy harvesting and storage.^{27,28} Although the material was known for a long time,²⁹ Wang *et al.* first reported the photocatalytic activity of g-C₃N₄ in 2009.³⁰ Ever since then, we have seen many reports on the profuse applications of g-C₃N₄ regarding photocatalytic H₂ production,³¹⁻³³ pollutant degradation,^{34,35} CO₂ reduction,^{36,37} *etc.* The suitable electronic band structure, visible light absorption capability, non-toxicity, and easy synthesis from low-cost precursors render g-C₃N₄ an ideal photoelectrode material for energy harvesting. The photocurrent responses of carbon nitride solids were first reported by Zhang *et al.*³⁸ in 2010, paving a new path for PEC applications.³⁹ Several reports covering various aspects of g-C₃N₄-based PEC water splitting are available in the literature,³⁹⁻⁴⁵ most of which are primarily focused on film fabrication strategies. In this review, we provide a concise depiction of the basic



Suja Haridas

Suja Haridas obtained her PhD from Department of Applied Chemistry, Cochin University of Science and Technology in 2002. She is currently an Associate Professor, Department of Applied Chemistry, CUSAT, Kerala. Her research interests include heterogeneous catalysis and photocatalysis as well as 2D materials for energy harvesting, storage and membrane technology.



Challapalli Subrahmanyam

Challapalli Subrahmanyam obtained his PhD in Chemistry from the Indian Institute of Technology, Madras, in 2003. From 2003 to 2007, he was a post-doctoral fellow in the École Polytechnique Fédérale de Lausanne, Switzerland. He started his academic career as an Assistant Professor at the National Institute of Technology Trichy, India. In 2009, he moved to the Indian Institute of Technology, Hyderabad, as an Assistant Professor, where he is currently a professor of Chemistry. His research focuses on nanomaterials for solar energy harvesting and environmental remediation.



Sebastian Nybin Remello

Dr Sebastian Nybin Remello joined the Department of Chemistry as an Assistant Professor in 2017. He received his PhD (Applied Chemistry) in 2015 from the Department of Applied Chemistry, Tokyo Metropolitan University, Tokyo. From 2015-2017, he worked as a postdoctoral research fellow at the Center for Artificial Photosynthesis, Tokyo Metropolitan University. His primary area of research is the development of chemical architectures for artificial photosynthesis based on metal porphyrins and metal-organic frameworks.



principles of photoelectrochemical water splitting. A brief recap of the potential of g-C₃N₄ as a photo(electrocatalyst) and the various electrode fabrication strategies are provided. The focus here is an in-depth overview of the prevailing status of g-C₃N₄-based photocathodic and photoanodic materials for PEC water splitting. The prospects and challenges are highlighted in the concluding section.




1.1 Hydrogen economy

The development of a hydrogen economy is mankind's finest opportunity for a sustainable energy future considering the rising expense of fossil fuels and concerns about energy security and environmental safety.⁴⁶ The hydrogen economy refers to an industrial system where electricity and hydrogen are the two universal energy carriers.⁴⁷ In recent decades, there has been a notable surge in interest in hydrogen as a potential energy carrier for a sustainable future. With a low heating value, hydrogen combustion releases more energy than any other fuel when compared mass-wise. Presently, the reforming of fossil fuels accounts for 98% of the annual output of H₂, which is about 0.1 Gton.⁴⁸ The most significant advantage of using hydrogen is that when it burns with oxygen, it generates heat and water, unlike fossil fuels, which release carbon dioxide.⁴⁹ A 'low-carbon future' will arise from the development of the hydrogen economy. This will lower greenhouse gas emissions globally, which will mitigate their detrimental effects on the climate. As the hydrogen economy progresses, 'green' hydrogen is perhaps the most envisaged form of hydrogen. Hydrogen produced by electrolyzing water using renewable solar energy is green hydrogen, which has zero carbon emissions.^{50,51} Despite making up a very small portion of the energy output at the moment, H₂ generation from renewable resources has enormous potential to cover the world's energy needs without having a negative environmental impact.⁴⁶ Since the costs of these technologies are still too expensive in comparison to traditional fossil fuel-based technologies, their real-time deployment will require both considerable technology advancements and cost reductions. Innovations in technology are particularly required in the areas of storage, transportation, carbon capture and the low-efficiency hydrogen generation from renewable sources.⁴⁹

1.2 Basics of PEC water splitting

Solar-assisted PEC water splitting is contemplated as a promising approach for sustainable energy production. The basic principle of PEC water splitting involves hydrogen generation utilising solar energy and is aided by an external bias between the semiconductor photoelectrode and a counter electrode in the presence of a suitable electrolyte. The external bias enables the slow kinetics to be overcome and drives the reaction at a desired rate/current density.⁵² PEC water splitting is mainly comprised of two half-reactions, water oxidation or oxygen evolution reaction (OER) at the anode and water reduction or hydrogen evolution reaction (HER) at the cathode. Overall, water splitting can be represented as follows: water splitting is an energy-uphill process with a ΔG value of 237 kJ mol⁻¹,

rendering it thermodynamically unfavourable.⁵³ The feasibility of the reaction demands a minimum energy requirement of 1.23 eV.⁴¹ Therefore, the semiconductor photoelectrode should be able to absorb light energy equivalent to or greater than 1.23 V and subsequently generate electron-hole pairs. In order to initiate the overall water splitting, the valence band (VB) maximum of the photocatalyst should be more positive than the water oxidation potential ($E_{\text{ox}}^0 = 1.23$ eV at pH 0), and the conduction band (CB) minimum should be more negative than the hydrogen evolution potential ($E_{\text{red}}^0 = 0$ eV at pH 0).^{2,54} Thus, the wavelength employed, along with the band edge positions of the catalyst, plays a critical role in deciding the efficiency of overall water splitting. The photoinduced physical and chemical processes involved include light absorption, charge separation and migration, charge injection and the corresponding chemical reactions at the electrode.^{8,13,26} The efficiency of the process is heavily reliant on the charge transfer at the electrode/electrolyte interface. The electrode materials, depending on their nature, fall under the categories of photoanodes or photocathodes. The electrodes perform the dual roles of light-absorbing antennae promoting electron-hole generation, and active sites for H₂/O₂ evolution. Generally, n-type semiconductors are employed as photoanodes with the Fermi level being closer to the CB minimum. Photocathodes are usually made of p-type semiconductors, with their Fermi level being closer to the VB maximum. When immersed in an electrolyte, there occurs a shift in the Fermi level resulting in the formation of an electric field and a consequent band bending. In the case of n-type semiconductors, we have an upward bending while a downward bending is observed for p-type materials.³⁸⁻⁴² In short, the transfer of electrons to the electrolyte by a p-type semiconductor generates a cathodic photocurrent, while an anodic photocurrent is produced when holes are received by the electrolyte aided by an n-type semiconductor.⁵³ The electrons generated at the CB of the photocathode directly migrate to the electrode surface, reducing H⁺ to H₂, while holes are transported to the anode for water oxidation.^{40,41,52,53,55} In the case of the photoanodes, oxygen is evolved due to direct water oxidation by holes. The electrons generated at the anode are directed to the cathode *via* an external circuit. H⁺ migrates to the cathode to be eventually reduced to H₂.^{8,40,52,53} During the charge migration process, overpotential results from the energy losses occurring when electrons migrate through the external circuit and holes through the space charge region.



The general device setup consists of a photoelectrode (cathode/anode), a counter electrode (usually platinum), a suitable electrolyte, and a wire completing the circuit. Semiconductor PEC water splitting may be achieved *via* single or coupled



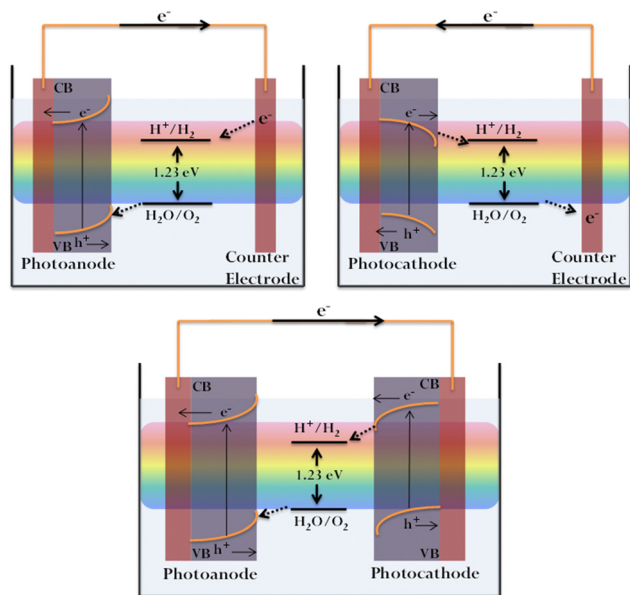


Fig. 1 Schematic representation of PEC water-splitting cells with single and coupled photosystems.

photosystems. In the former case, either the anode or cathode is photoactive, with Pt being the traditional commonly used counter electrode. For the coupled (tandem) photosystems, n- and p-type semiconductors are used as the anode and cathode, respectively (Fig. 1).⁵⁵

1.3 Relevant challenges and attempts for improved PEC performance

The semiconducting photoelectrodes are the vital constituents of a PEC system. A flawless photoelectrode material should meet several requirements, including a low band gap, efficient charge carrier utilization, low overpotential, wide solar spectrum harvesting, excellent stability for extended operation, and facile low-cost fabrication to enable commercialisation. The search is still ongoing to explore new photoelectrode materials exhibiting sustainable PEC performance.^{56,57} Recently, several semiconductor materials have been acclaimed as effective photoelectrodes, including oxides, nitrides and sulphides such as TiO_2 , BiVO_4 , WO_3 , Fe_2O_3 , ZnO , Ta_3N_5 , $g\text{-C}_3\text{N}_4$, MoS_2 , WS_2 , etc.^{15–20,23–26,58,59} Nevertheless, none of them fulfils the requirements for large-scale synthesis and hydrogen generation. The efficiency of hydrogen evolution is dependent on the characteristics of the semiconductor material, including its specific surface area, surface planes, morphology, and optical qualities. The photocatalyst's light absorption range is a property of the semiconductor band gap, whereas the viability for simultaneous water oxidation and reduction is reliant on the conduction and valence band positions.² On the other hand, if the material exhibits optimum photocurrent densities, photocorrosion-related stability problems will prevent it from performing for industrial-scale applicability. Unresolved issues including limited catalyst stability and inadequate efficiency are related to the physicochemical characteristics of the semiconductor material.

The fabrication of novel materials and the improvisation of current photocatalyst materials through structural and chemical modifications will enable the large-scale generation of hydrogen from solar energy in an efficient manner.² Some of the key design strategies that can be employed to improve the overall performance of the photoelectrodes are listed here.

- The construction of heterojunctions is one of the most frequently utilized techniques for averting charge recombination. A relative shift in band position may be seen when two semiconductors with thermodynamically matched band structures come into contact, causing the band to bend at the interface. By combining a narrow band gap semiconductor with a broad band gap scaffold, light absorption could be enhanced in addition to the internal electric field that improves the charge separation efficiency.^{60,61}

- PEC performance has been successfully boosted by tuning the semiconductor materials into several morphologies, including nano-rods/wires, nano-flakes, nanotubes, and nano-porous structures. The condensed material geometry provides a shortcut for the charge transport process in addition to having an accessible area for electrolyte interaction.^{60,62,63}

- Heteroatom doping, as demonstrated by theoretical and experimental research, can concurrently improve electrical and light absorption characteristics by generating shallow donor and/or acceptor levels.⁶ While employing this tactic, some cases have reported increased donor density and conductivity, while other cases have succeeded in modifying the band gap or even the band structure. However, controlled doping remains challenging.^{60,64,65}

- One effective way to raise the photovoltage is to deposit passivation overlayers, which are either a wide band gap semiconductor coating or a layer of extremely thin, comparatively insulating metal oxide. It is used in hematite photoanodes more frequently, which triggers band bending, boosts photovoltage and decreases onset potential.⁶⁶

- The photocorrosion of semiconductor materials, which happens when photogenerated charges drive the material self-oxidation (or reduction) instead of the water-splitting reaction, is one of the major causes of instability in PEC devices.⁶⁷ Apart from photocorrosion, there are additional variables that contribute to the instability of PEC water-splitting devices, which are associated with the interfaces between the electrolytes and semiconductor catalysts. Finding materials that are inherently resistant to corrosion remains a potential milestone and is one way to attain high stability; another is to use protective layers that can physically separate the semiconductor materials from the electrolyte. PEC device stability may be impacted by electrolyte conditions (pH, for example); adjusting the electrolyte composition and controlling the dissolution reaction during PEC operation can also help in the stable operation of PEC devices.⁶

- An approach that shows promise for addressing problems with single or heterojunction PEC devices is tandem cell configuration. PEC systems can offer higher STH by harvesting a broader solar spectrum in tandem cell configuration. Photoanode/photocathode (PEC/PEC) and photoelectrode/photovoltaic



(PEC/PV) tandem cells are the two primary types of tandem cell configuration. These tandem dual-absorber devices can maximize the amount of solar energy absorbed while also producing a strong driving force for self-driven solar water splitting. Sunlight first passes through the n-type semiconductor and then the p-type semiconductor in a PEC/PEC tandem cell. The top electrode, the photoanode, absorbs photons with shorter wavelengths in the solar spectrum. The bottom electrode, the photocathode, transmits and collects the remaining photons with longer wavelengths. Thermodynamically, two semiconductors with smaller band gaps can be selected in preference to a single photoelectrode since each photoelectrode only needs to supply a portion of the total potential for water splitting; yet, their stability remains a major concern when in direct contact with electrolytes. A voltage-biased PEC device with an integrated PV device constitutes a PEC/PV tandem cell. The semiconductor material's minority carriers in the PEC photoelectrodes in this configuration take part in the water redox reaction, which happens at the semiconductor–electrolyte junction. When there is insufficient power produced by the minority carriers, solar cells can sustain an operation. Like the PEC/PEC arrangement, light serves as the only energy input for the entire system.^{11,68–70}

1.4 $g\text{-C}_3\text{N}_4$ as a potential water-splitting photo(electro)catalyst

$g\text{-C}_3\text{N}_4$ has a layered graphite-like structure consisting of tri-s-triazine units (Fig. 2). The simplistic synthesis route from low-cost precursors, chemical/thermal stability, non-toxicity, and biocompatibility have contributed to the wide interest in the material.

With the VB and CB positions being favourable for both water oxidation and reduction potentials, $g\text{-C}_3\text{N}_4$ has attracted great interest as a photo(electro)catalyst. Moreover, $g\text{-C}_3\text{N}_4$ shows resistance to photocorrosion.⁷¹ However, the inherent activity is restricted by the limited visible light sensitivity, low surface area, poor electronic conductivity and fast electron–hole recombination. Considerable effort has been directed towards enhancing the performance by lengthening the exciton diffusion length to prevent charge recombination at grain boundaries. Tuning the electronic structure *via* heteroatom doping (metal/non-metal) can alter the absorption edge, enhancing the visible light sensitivity.^{72–76} Non-metal species substituting

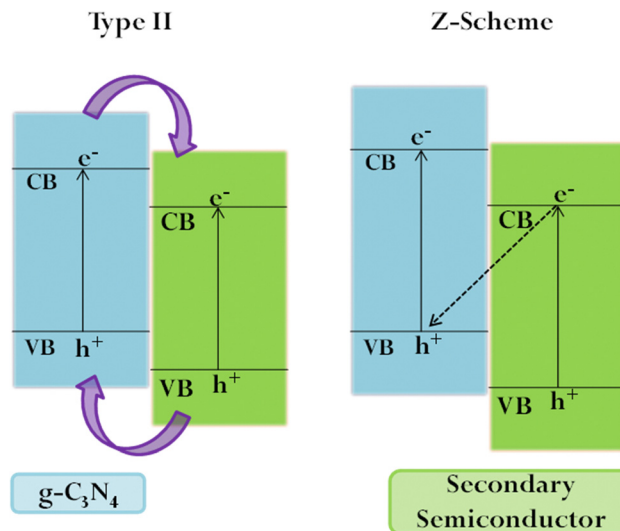


Fig. 3 A graphic illustration of type II and Z-scheme heterojunctions.

carbon and nitrogen in the framework promote charge separation and migration, while metal atoms are substituted in interstitial spaces, thereby introducing defect sites and additional atomic orbitals, which in turn alter the absorption edge.^{74,77,78} It needs to be mentioned that excessive doping retards PEC performance by providing sites for charge recombination and triggering side reactions.⁷⁹ Creating an efficient heterojunction enables the fast migration of charges at the interface, prolonging the exciton lifetime.⁸⁰ The most commonly used ones are Z-scheme and Type II heterojunctions (Fig. 3), which achieve efficient separation of photogenerated electrons and holes, ensuring sustainability. The order of deposition plays a major role in deciding the electron flow and the type of heterojunction formed.⁸¹ As compared to nanoparticles, ordered nanoarrays have been found to promote charge migration, inhibiting recombination at grain boundaries.^{41,82,83} Morphological and crystalline factors are also quite crucial in deciding the band gap and charge separation.^{53,84,85} The introduction of localised surface plasmon resonance also enhances PEC efficiency.^{86–89} It has been reported that combining $g\text{-C}_3\text{N}_4$ with other carbon compounds and dye sensitization increases its activity.^{90–92}

2. Electrode fabrication strategies

The fabrication of thin films of $g\text{-C}_3\text{N}_4$ is a salient step in PEC water splitting. One of the major factors affecting the PEC application of $g\text{-C}_3\text{N}_4$ is the difficulty encountered in fabricating uniform high-quality films on the conductive substrate.^{44,52} The formation of thin and uniform films of $g\text{-C}_3\text{N}_4$ is difficult because of its poor dispersibility/solubility in most of the solvents and subsequent aggregation leads to cracks and non-homogeneous film. Poor adhesive forces between $g\text{-C}_3\text{N}_4$ also contribute to the inhomogeneous microstructures of the photoelectrodes leading to a low photocurrent density. There are two types of methods for thin film fabrication: top-down and bottom-up. The top-down approaches to film fabrication

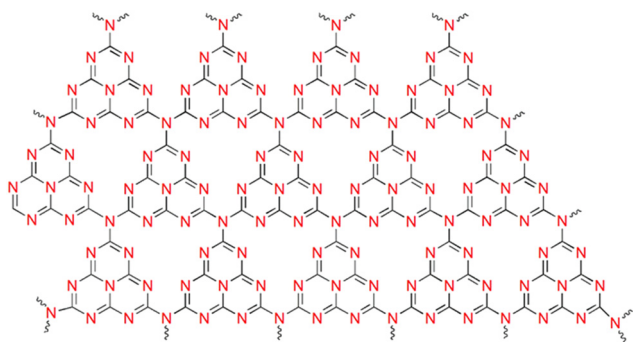


Fig. 2 Schematic illustration of $g\text{-C}_3\text{N}_4$ containing tris-s-triazine units.



include drop casting,^{89,93–100} spin coating,^{101–105} dip coating,¹⁰⁶ spray coating,¹⁰⁷ vacuum filtration,^{108–112} electrospinning,^{113–115} doctor blade,^{116,117} *etc.* It is exceedingly difficult to create a uniform and stable slurry or sol of g-C₃N₄ while employing top-down techniques, which often leads to massive aggregations of g-C₃N₄ and cracks in the film as well as the interface between the film and substrate. As a result, PEC performance is frequently low in such top-down manufactured g-C₃N₄ film photoelectrodes.³⁹ The casting of g-C₃N₄ embedded in a conductive polymer matrix improves charge transport and casting homogeneity.¹¹⁸

Several advanced bottom-up approaches have been adopted to enhance the PEC performance of the photoelectrodes by achieving high-quality g-C₃N₄ films. These techniques favour the formation of uniform micro-structured films with intimate contact with the substrate, thereby facilitating smooth charge transfer. The bottom-up approach also enables to mitigate the problem of poor dispersibility of g-C₃N₄. Electrochemical deposition, a commonly used bottom-up approach can be categorised into electrophoretic deposition^{119–121} and electrodeposition.^{122–124} Electrophoretic deposition is achieved by holding the substrates at the positive and negative potential in a dispersion of exfoliated g-C₃N₄.¹¹⁹ The strategy avoids high-temperature operation, enabling deposition on thermally unstable substrates like carbon paper and nickel foam, which is essential for flexible film fabrication. Thermal vapour condensation (TVC) involves the direct vaporisation of the solid precursors and deposition as a thin film over the substrate and subsequent polymerisation under controlled thermal conditions^{125–137} quite similar to the chemical vapour deposition (CVD) technique. The careful temperature control enables the fine-tuning of the morphological characteristics and micro-structure of g-C₃N₄ films. The major advantage of TVC is the non-requirement of sophisticated instrumentation. However, precursors like urea, thiourea, cyanamide, *etc.*, are reported to form coarse low-quality films leading to high dark currents.^{133,138} Unlike thermal vaporisation, the direct growth method involves direct contact between the substrate and precursor and its transformation into film over the substrate by thermal polymerisation. Here also, deposition on a variety of substrates like FTO, ITO, *etc.*, is possible. Furthermore, it is feasible to create a variety of morphologies, such as thick films, porous films, or nanorod arrays for g-C₃N₄ films using this method.^{139,140} Hetero-films can also be conveniently fabricated *via* vaporization-assisted thermal polymerization. Similarly, choosing special substrates allows the deposition of a continuous film *via* the intermediate formation of a supramolecular complex.^{139,141,142} The thin films fabricated using liquid-mediated growth exhibited high mechanical robustness, yielding films that resisted peel-off even after ultrasonication.¹⁴² The microcontact-printing-assisted process involves the infiltration of precursor (cyanamide) solution into the anodic aluminium oxide membrane (AAO) placed between FTO substrates.^{143,144} At high temperatures, cyanamide vapours released from AAO diffuse over to the substrates and are deposited as g-C₃N₄ films after thermal polymerisation. The protocol allows the control of film thickness by varying the cyanamide concentration.

Solvothermal deposition followed by annealing has also been charted as a convenient route for the fabrication of C₃N₄ films.^{144–146} The annealing enables the tri-*s*-triazine structure formation and improves film crystallinity. Altering the precursor concentration, treatment time and post-annealing temperature can control the film thickness and density. The solvothermal route ensures intimate contact between the substrate and the precursors and hence provides better adhesion of the film leading to an enhanced photocurrent.

3. PEC performance of g-C₃N₄ electrodes

The unbiased Fermi level (E_F) position of g-C₃N₄ renders it suitable for application as either the photoanode or the photocathode material for PEC water splitting. The following sections focus on the utility of g-C₃N₄ as photoanodes and photocathodes. The literature reports on photocathodes are relatively few, perhaps due to slow reaction dynamics.

3.1 Pristine and modified graphitic carbon nitride as photoanodes

Although g-C₃N₄ is a promising n-type semiconducting material with appropriate band edge positions, the PEC performance of neat g-C₃N₄ remains low and challenging and efforts have been made to devise strategies for morphological control to obtain a greater photoresponse. The morphological transformation from nanoplates to nanorods *via* controlled reflux resulted in a two-fold enhancement in photocurrent.¹⁴⁷ The alteration from nanoplates to nanorods *via* a sequential exfoliation, regrowth and rolling of lamellar sheets was believed to eliminate the surface defects and increase the active lattice face. DFT studies also supported the stability of the tri-*s*-triazine structure in comparison to the *s*-triazine structure.

Acid exfoliation of bulk g-C₃N₄ could yield a porous honeycomb structure causing a rapid decrease in electron-hole pair recombination.¹⁴⁸ The first successful attempt at microcontact printing-assisted growth over an anodic aluminium oxide (AAO) membrane was reported by Liu *et al.*¹⁴⁴ The random and even diffusion of cyanamide vapours onto the upper and lower substrates resulted in a uniform graphitic carbon nitride network over FTO plates yielding a photocurrent density of 30.2 $\mu\text{A cm}^{-2}$ at 1.23 V_{RHE}. This was ascribed to an advanced microstructure, intimate contact with the conducting substrate, ultrathin film thickness and a high proportion of exposed active sites. Uniform g-C₃N₄ films prepared by thermal vapour condensation from melamine precursors exhibited a high photocurrent density in comparison with bulk g-C₃N₄.^{129,133} The high performance was attributed to intimate contact with the substrate, lower charge transfer resistance and reduced electron-hole recombination. The treatment temperature was crucial and relatively smooth transient photocurrents indicated the balanced photo-charge generation and transport process while decay denoted a high probability of charge recombination.



The deposition of FeOOH as a cocatalyst improved the charge transfer rate, giving a high photocurrent.¹³³

Zhang *et al.* reported enhanced photocurrent generation in protonated $g\text{-C}_3\text{N}_4$ and the protonation was reported to facilitate the dispersion of C_3N_4 .¹⁴⁹ An *in situ* solvothermal direct growth of $g\text{-C}_3\text{N}_4$ film on an FTO substrate generated a four-fold activity enhancement as compared to post-processed films because of enhanced adhesion and compactness leading to better device performance.¹⁴⁷ Mild annealing in a nitrogen atmosphere was crucial in forming a perfect film. The PEC property of ultrathin flakes of $g\text{-C}_3\text{N}_4$ synthesised by a wet mechanical grinding method was reported to be greater as compared to bulk $g\text{-C}_3\text{N}_4$ due to two possible reasons: a more positive VB potential and the enhanced electron transfer ability in the horizontal plane prolonging the lifetime of the photo-generated electrons.¹⁵⁰ Pinhole-free $g\text{-C}_3\text{N}_4$ films were obtained using a two-step vapour deposition process (TVD) from various precursors, and a photon-induced oxygen evolution upon anodic polarization in aqueous electrolytes resulted in a photocurrent density of $63 \mu\text{A cm}^{-2}$ at $1.23 V_{\text{RHE}}$ bias.¹⁰³ The quality of the films depended on the nature of the substrate, the monomer amount and the deposition temperature. A lower charge transfer resistance at the electrode/electrolyte interface may be ascribed to the enhanced thermal condensation degree of the film prompting the continuous growth of the films. Peng *et al.* fabricated a closely packed $g\text{-C}_3\text{N}_4$ film by crystallisation of $g\text{-C}_3\text{N}_4$ monomers followed by thermal condensation.¹⁵¹ The seeded FTO plate was immersed in a hot aqueous supersaturated solution of melamine to prompt further deposition of melamine during cooling followed by calcination to obtain the $g\text{-C}_3\text{N}_4$ film. Seeding-induced deposition eventually resulted in the formation of a dense highly interconnected porous layer firmly adhered to the substrate, leading to a low onset potential of $0.25 V_{\text{RHE}}$. The electrodes also exhibited excellent hole extraction efficiency, promoting exciton dissociation *via* the template confinement along with improved electrode stability. A high IPCE value of around 15% was demonstrated with illumination at 360 nm in a neutral medium without a sacrificial agent.

Monolayered $g\text{-C}_3\text{N}_4$ spin-coated onto FTO from a methanolic dispersion of bulk $g\text{-C}_3\text{N}_4$ retained its intrinsic n-type properties and activation under positive applied bias-enhanced PEC performance.^{102,152} The interaction of the C and N atoms with methanol molecules and the cavitation effects of ultrasonication led to ultrafast drying and disruption of the van der Waals forces within the $g\text{-C}_3\text{N}_4$ structure. The negative shifting of the conduction band (CB) and valence band (VB) potentials in exfoliated $g\text{-C}_3\text{N}_4$ indicated the possibility of Z-scheme heterojunction construction. Qin *et al.* demonstrated the direct growth of carbon nitride films with extended optical absorption, excellent charge separation under illumination and outstanding performance as the photoanode, yielding 51% faradaic efficiency for O_2 and an external quantum yield of 12% at $1.23 V_{\text{RHE}}$ in alkaline solution and quantum efficiency of around 8.5% at 400 nm without sacrificial agents. In comparison with its bulk counterpart, the nanostructured $g\text{-C}_3\text{N}_4$ exhibits a

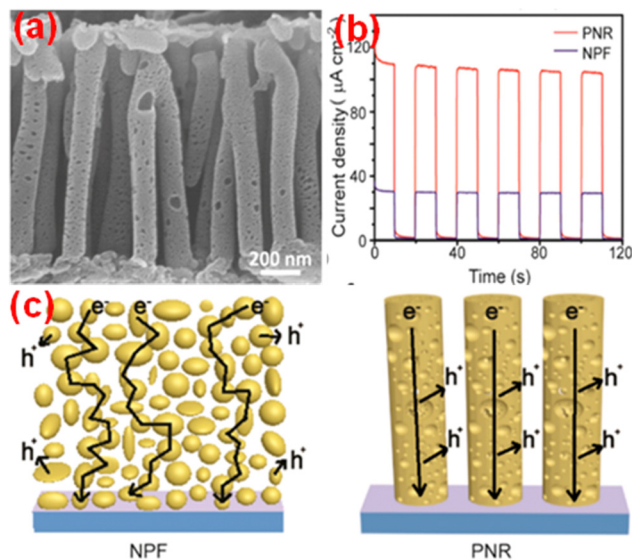


Fig. 4 (a) SEM images, (b) transient photocurrent density curves and (c) schematic diagrams showing the transport pathway of electrons in the NPF and PNR of $g\text{-C}_3\text{N}_4$. Reprinted from ref. 154 with permission.

high degree of aromatic ring π -conjugation, enhancing the charge carrier mobility, and the creation of a large proportion of hole-accepting defect sites and space charge regions (SCR) boosts the PEC activity.¹⁵³ A high open circuit voltage of 0.61 V indicated the good charge separation characteristics of the electrode. A photoanode based on a vertically aligned $g\text{-C}_3\text{N}_4$ porous nanorod array (PNR) prepared *in situ* using a thermal polycondensation approach, with anodic aluminium oxide as the template, could yield a photocurrent density of $120.5 \mu\text{A cm}^{-2}$ at $1.23 V_{\text{RHE}}$ under solar illumination. The SEM images, transient photocurrent density curves and schematic illustrations showing the transport pathway of electrons in the NPF and PNR of $g\text{-C}_3\text{N}_4$ are given in Fig. 4.¹⁵⁴

3.1.1 Heteroatom doping. Successful deposition of S-doped $g\text{-C}_3\text{N}_4$ films on ITO conductive substrates could be achieved by mixing thiourea into melamine as a co-precursor *via* a CVD route.¹⁴⁰ Apart from introducing sulphur into the matrix, thiourea is proposed to affect the crystallinity and morphology of the films by modulating the polymerisation mode. A negative shift in the open circuit potential indicated the transfer of photogenerated electrons to the counter electrode *via* an external circuit, confirming the n-type behaviour of the electrode. To compensate for the low photocurrent insufficient for O_2 evolution, the feasible construction of n-p heterojunctions as photoanode and n-n heterojunction as photocathode is suggested. The role of S in the initialisation of film growth and in assisting charge migration was proposed by Fang *et al.*¹⁵⁵ A photocurrent of $100 \mu\text{A cm}^{-2}$ at $1.23 V_{\text{RHE}}$ under AM 1.5 illumination in NaOH electrolyte without a sacrificial agent has been reported. The performance was attributed to the reduced defects along the interface inhibiting charge recombination.¹⁵⁵ Gradient doping of S by molten mediated polymerisation for a gradually varying band structure to promote charge separation and PEC performance in an alkaline



medium was demonstrated by Fang *et al.*¹⁵⁶ P and S-doped 1D-g-C₃N₄ prepared using a modified hydrothermal synthesis exhibited high water oxidation capability.¹⁵⁷ Enhanced charge separation and subsequent prolonging of the lifetime of charge carriers resulted in the charge accumulation at the electrode surface and transfer to the electrolyte yielding a higher water photo-oxidation current as compared to undoped 3D and 1D-g-C₃N₄. The promotion of PEC activity by the synergistic effect of heteroatom doping/heterojunction formation/cocatalyst deposition on interfacial charge transfer has also been demonstrated.^{158–165}

A drastic narrowing of the bandgap in P-doped g-C₃N₄ enabled near-infrared light-induced PEC water splitting, generating a photocurrent density of 1.4 $\mu\text{A cm}^{-2}$ at 1.2 V_{Ag/AgCl} and H₂ evolution of 1.27 $\mu\text{mol h}^{-1} \text{g}^{-1}$ at 0.6 V with reference to the Ag/AgCl electrode.¹⁶⁶ The delocalisation of the isolated electrons into the π -conjugated structure of g-C₃N₄, generated a positively charged centre at the P atom inhibiting the charge recombination. A novel B-C₃N₄/bulk g-C₃N₄ heterojunction architecture with 10% IPCE and 103.2 $\mu\text{A cm}^{-2}$ at 1.23 V_{RHE} was reported by Ruan *et al.*¹³⁷ Theoretical and experimental investigations indicated an upward shifting of the VB edge and a lowering of the bandgap enabling the hole transfer from the bulk to the surface for photooxidation/hydrogen evolution and enhanced PEC activity.^{72,137} The results of PEC measurements from ref. 72 are represented in Fig. 5. A high level of boron doping induced the formation of defect centres promoting electron-hole recombination. The negligible impact of H₂O₂ addition on the photocurrent proves the inherent charge separation in the photoanode. The localisation of HOMO (VB) onto two heptazines and the delocalisation of LUMO (CB) was proposed by the theoretical studies indicating the possible pathway of suppression of electron-hole recombination. Lei *et al.* constructed a g-C₃N₄/B-doped g-C₃N₄ (BCN) 2D heterojunction photoanode, which intensified the interfacial contact area between BCN and the porous g-C₃N₄ and shortened the transfer time and diffusion pathlength of photogenerated charge carriers.¹⁶¹ A heat treatment strategy was used for the preparation of B-doped graphitic carbon dots/C rich g-C₃N₄ heterojunction composites with higher photocatalytic and photoelectrochemical activity.¹⁶²

V-doped g-C₃N₄ prepared by the direct calcination of urea and ammonium metavanadate exhibited enhanced light absorption and charge separation, and high water-splitting

activity.¹⁶⁷ Doping with cobalt resulted in the VB being shifted to more positive values and a negative shift of the CB edge, improving the PEC performance.^{84,168} The red shift in the absorption edge enhanced the light-harvesting capability, and improved interfacial charge transfer was established from the EIS analysis, with Co²⁺ acting as an electron trap. The role of Co in promoting O₂ evolution was also reported.¹⁶⁸ Pd and Ag-doped C₃N₄ nanostructures electrophoretically deposited on FTO for photoelectrocatalytic oxygen evolution under simulated solar radiation have been tested.¹⁶⁹ Dip coating of Ni(OH)₂ further improved the performance. An increased band bending at the band edge and facilitated electron transfer at the electrode/electrolyte interface enhanced the surface oxidation kinetics. Zhao *et al.* devised an ionic liquid-assisted protocol for the synthesis of Br-modified g-C₃N₄ with high surface area and porous structure.¹⁷⁰ The enhanced transportation capability of photogenerated electrons and improved optical/conductive properties are attributes of high H₂ evolution capability. Significant enhancement in the photoelectrochemical properties was achieved by the insertion of Ni ions into the phenyl-modified graphitic carbon nitride layer.⁷⁵ Interactions between Ni and precursor molecules in the molten state, prior to condensation, contributed to the homogeneous dispersion of Ni, leading to extended light absorption and charge transfer, culminating in enhanced PEC performance. The reduction in the bandgap after bismuth doping is linked to the formation of localized isolated energy levels below the CB minima of pristine C₃N₄.¹⁰² Bi-doping of g-C₃N₄ significantly favors the charge separation and electron transfer from the surface of the photoanode to the electrolyte, with the PEC performance being strongly dependent on optimal Bi content. To enrich the photoactivity, Paul *et al.* adopted the co-doping of Mg and Li atoms into the g-C₃N₄ matrix, resulting in a greater photo response as compared to its metallic counterparts.¹⁷¹

3.1.2 Carbon materials. Carbon materials can act as excellent matrices facilitating electron transfer to enhance PEC performance. Carbon nanomaterial insertion is proposed to provide orthogonalization of light resulting in enhanced light absorption.¹⁷² The PEC performance of g-C₃N₄ was improved through the efficient charge cascade achieved by Bi doping along with the use of GO as a cocatalyst on the surface of the photoanode.¹⁶⁵ A low Tafel slope and better interfacial charge transfer prospects revealed by EIS and PL analysis account for better electrode kinetics and reduced activation energy barrier for the OER. The development of a highly porous interconnected g-C₃N₄/r-GO photoanode with long electron diffusion length ($\approx 36 \mu\text{m}$), large electrochemically active surface area, enhanced light harvesting, and hole extraction property was reported by Peng *et al.*¹¹⁶ Better interfacial charge transfer and excellent electron mobility led to a 20-fold enhancement in photocurrent density, a high external quantum efficiency of $\approx 5\%$ at 400 nm and stability over a wide pH range. A porous graphitic carbon nitride/reduced graphene oxide (r-GO) interface constructed *via* a solvothermal route and deposited on a Ni foam created a highly active photoanode, with r-GO acting as the bridge for accelerating the rate of electron transfer from

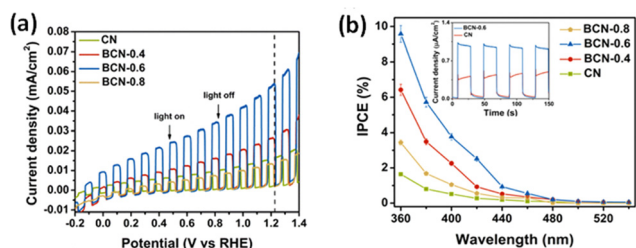


Fig. 5 (a) The light-chopped LSV curves in 0.2 M Na₂SO₄ and 0.05 M Na₂S (pH = 11.7). (b) The IPCE with transient photocurrent density curves under visible light ($\lambda > 420 \text{ nm}$) (inset). Reprinted from ref. 72 with permission.



$g\text{-C}_3\text{N}_4$ to Ni foam.¹⁷³ The efficient transfer of the hot electrons generated from $g\text{-C}_3\text{N}_4$ under visible light illumination to the cathode was efficiently driven by r-GO and external bias potential. $g\text{-C}_3\text{N}_4/\text{CNT}$ composite films with enhanced PEC properties were fabricated by Yousefzadeh *et al.*¹⁷⁴ The mechanism proposed involves water oxidation by the holes. CNT promotes the transport of the photoelectrons from the $g\text{-C}_3\text{N}_4$ nanoparticles to the counter Pt electrode *via* the FTO substrate, leading to water reduction. A metal-free flexible protonated $g\text{-C}_3\text{N}_4/\text{C}$ dots photoanode fabricated on a polyethylene terephthalate (PET)/indium tin oxide substrate (ITO) by the electrophoretic approach generated a photocurrent of $38 \mu\text{A cm}^{-2}$ at $1 V_{\text{RHE}}$.¹⁷⁵ The narrow band gap sp^2 carbon clusters contributed to excellent light absorption and a negative shift in the onset potential.

3.1.3 Metal oxides. TiO_2 has been one of the most explored wide-bandgap materials. Heterojunction formation with $g\text{-C}_3\text{N}_4$ along with enhancing the visible light sensitivity improves charge separation and enhances the PEC performance.¹⁷⁶ As compared to TiO_2 nanocrystal-based films, unique nanotube arrays are found to exhibit higher photon collection efficiency and better charge separation.^{177,178} $g\text{-C}_3\text{N}_4$ and TiO_2 nanotube arrays with 7.3% IPCE at a wavelength of 400 nm were fabricated by Zhou *et al.*¹⁷⁹ Direct Ti–O–C bonding resulted in unique electronic coupling and enhanced optical absorption.¹³⁴ Electron injection from the LUMO of $g\text{-C}_3\text{N}_4$ to the CB of TiO_2 offers efficient charge separation and the coupled system can be regarded as a “dyad”. A photoanode comprised of $g\text{-C}_3\text{N}_4\text{-TiO}_2$ nanotube arrays with UV and near-UV sensitivity was fabricated by the *in situ* growth of $g\text{-C}_3\text{N}_4$ on the surface of TiO_2 nanotubes, resulting in a six-fold enhancement in photocurrent density and hydrogen evolution of $19.1 \mu\text{mol h}^{-1}$.¹⁸⁰ Cu implantation enhanced the electronic conductivity and electronic structure of TiO_2 nanotube arrays (TNA), causing a significant lowering of the band gap, and further decoration with polymeric carbon nitride nanosheets (PCN) enhanced visible light absorption and exciton separation at the heterojunction. Cu implantation generates Ti^{3+} in TiO_2 crystals and enhances interfacial bonding between TiO_2 and PCN with a subsequent acceleration of charge transfer at the heterojunction. PCN decoration passivates the surface defects created by Cu implantation and reduces the surface trap density of the material enhancing exciton lifetime.¹⁸¹ Synthesis of TNAs by electrochemical anodization on a titanium substrate and the facile thermal treatment using suitable substrates for the formation of $g\text{-C}_3\text{N}_4/\text{TiO}_2$ heterojunction is one of the most adopted strategies.^{182–184} A diagram of the charge transfer mechanism of the $g\text{-C}_3\text{N}_4/\text{TNTA}$ heterojunction electrode and the photocurrent density of different photoanodes is given in Fig. 6.¹⁸⁴ The interaction involves the charge transfer from the electron-rich C_3N_4 surface and the unoccupied orbital of Ti^{4+} . The synergistic effects of Ti^{3+} and O-doping on the photoelectrochemical performance of Ti^{3+} self-doped $\text{TiO}_2/\text{oxygen-doped } g\text{-C}_3\text{N}_4$ ($\text{Ti}^{3+}\text{-TiO}_2/\text{O-}g\text{-C}_3\text{N}_4$) heterojunctions were examined.¹⁰³ C–O and O–C–N bonds in O– C_3N_4 can be bonded with hydroxyl groups of TiO_2 to form electron transfer pathways.

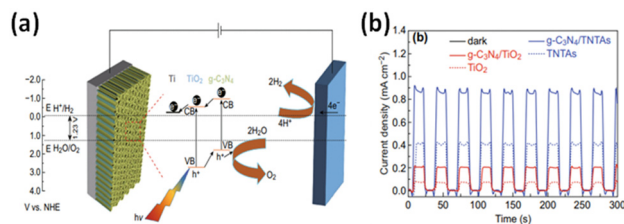


Fig. 6 (a) A schematic depiction of the charge transfer mechanism of the $g\text{-C}_3\text{N}_4/\text{TNTA}$ heterojunction electrode. (b) Time-dependent photocurrent density under intermittent light irradiation. Reprinted from ref. 184 with permission.

A core-shell $\text{TiO}_2/g\text{-C}_3\text{N}_4$ structure, obtained by the hydrothermal growth of TiO_2 nanorods and solvothermal growth of the $g\text{-C}_3\text{N}_4$ layer, was investigated by Fan *et al.*¹⁸⁵ $g\text{-C}_3\text{N}_4$ acts as a visible light absorption layer, while TiO_2 acts as an effective electron transfer layer hindering electron–hole recombination and improving the overall performance.¹⁸⁶ The construction of a Z-scheme heterostructure of TiO_2 with an interfacial oxygen vacancy layer and coupling with $g\text{-C}_3\text{N}_4$ has been investigated.^{187,188} The oxygen vacancies triggered the onset of an electronic band below the CB of pure TiO_2 . High donor density and a more negative flat band potential imply better photoelectrochemical performance. The enhanced photoelectrochemical performance of TiO_2 nanorod arrays/pillars decorated with $g\text{-C}_3\text{N}_4$ quantum dots has been verified by several groups.^{189–191} The synergistic effects of TiO_2 and C_3N_4 were established by DFT calculations.¹⁸⁹ Exposure to barbituric acid and the subsequent thermal polymerisation led to the substitution of N with C, producing reactive N-defect sites with an ensuing enhancement in PEC hydrogen evolution and exceptional stability for around 111 h under continuous illumination.¹⁹¹ Ultrathin red 2D- $g\text{-C}_3\text{N}_4$ (red CN) with a band gap of 2.05 eV enabling strong band-to-band visible light absorption was realised by the fluorination of ultrathin $g\text{-C}_3\text{N}_4$ followed by thermal defluorination.¹⁹² An intermediate defect band led to a lowering of the CB and the associated distribution of defect centres imparted high light-harvesting power and suppressed the recombination rate. A TiO_2 nanorod-based photoanode sensitized by red 2D CNs formed a type II band alignment showing a superior photocurrent density of $121.9 \mu\text{A cm}^{-2}$ at $1.23 V_{\text{RHE}}$ without the aid of a co-catalyst. A type II heterostructure between $g\text{-C}_3\text{N}_4$ nanoplatelets and TiO_2 giving a photocurrent density of $142.7 \mu\text{A cm}^{-2}$ at $1.23 V_{\text{RHE}}$ was reported by Rajaiitha *et al.*¹⁹³ A photoanode with a shell-core heterostructure of N-doped $\text{C}/g\text{-C}_3\text{N}_4/\text{TiO}_2$ generating a photocurrent density of 0.45 mA cm^{-2} at 0.6 V was constructed by Huang *et al.*¹⁹⁴

Improvement in electrical conductivity *via* reinforced contact between TiO_2 and $g\text{-C}_3\text{N}_4$ could be accomplished in a nitrogen-doped carbon (C_N) interfacial nano-layer derived from polydopamine. $g\text{-C}_3\text{N}_4$ -wrapped TiO_2 NTA heterojunction photoelectrodes with effective interfacial charge separation were fabricated *via* a chemical vapour deposition-like process.¹⁹⁵ Niobium doping has been a good strategy for altering the electronic



properties of TiO₂ due to the size compatibility of Nb⁵⁺ and Ti⁴⁺. Nb⁵⁺ replaces Ti⁴⁺ and the donor is formed on the TiO₂ conduction band, providing electrons for Ti⁴⁺ and obtaining high carrier concentration, enhancing the conductivity, and improving the PEC performance of the Nb-TiO₂/g-C₃N₄ photoanode.¹⁹⁶ The successful formation of a P-C₃N₄/TiO₂ heterojunction *via* sequential electrochemical anodization, wet dip coating and thermal polymerisation, and its efficient photocatalytic and photoelectrocatalytic performance has been demonstrated.¹⁵⁹ TiO₂ nanorods decorated with B-doped g-C₃N₄ were fabricated *via* the thermal polymerisation method to improve the PEC performance. The rational design of a hydrophilic bifunctional hierarchical assembly of B-doped g-C₃N₄ nanoplatelets with high visible light sensitivity and suppressed charge recombination was attempted by Ding *et al.*¹⁹⁷ The synergistic effect of B doping and the hydrophilic character, coupled with increased specific surface area and improved hierarchical porosity generated a photocurrent density of 1.72 mA cm⁻² at 1.23 V_{RHE} under AM 1.5G illumination. The modulation of the electronic structure was proposed to be *via* an orbital overlap between 2p levels of B and C in the VB and that of N and B in the CB. The synthesis of fluorine-doped g-C₃N₄ QDs (CNFQD) *via* a solid-state reaction and its further embedding into rutile TiO₂ by an *in situ* hydrothermal process could extend the photo response to 500 nm.¹⁹⁸ The energetics at the heterojunction were favourable for efficient electron transfer from CNFQDs to TiO₂ and hole transfer to the electrolyte under visible light irradiation. Modification of g-C₃N₄/TiO₂ with Co-Pi is reported to be a competent strategy for augmenting charge migration.^{199,200} Co-Pi incorporation does not change the band positions and the band gap was evidenced by the almost similar flat band potentials of g-C₃N₄/TiO₂ and Co-Pi-modified g-C₃N₄/TiO₂. The high PEC performance could be attributed to the fast interfacial charge migration from the photoanode to the electrolyte mediated by Co-Pi. The protective function of the TiO₂ layer and hole capture layer is also well demonstrated.²⁰⁰

Cobalt atoms when coordinated with g-C₃N₄ are reported to act as co-catalysts for water oxidation, leading to a photocurrent of 1.79 mA cm⁻² at 1.23 V_{RHE}.²⁰¹ The coordination was confirmed by the blue shift in the distinctive bending vibration of the tri-s-triazine unit ascribed to the weakening of the conjugation effect due to electron transfer from the π -conjugated ring to the empty d orbital of Co²⁺. The conversion of Co^{II} to Co^{III} and Co^{IV} mediated by photogenerated holes reduces the kinetic barrier for water oxidation and improves the water-splitting performance. The excellent PEC activity of the CuNi@g-C₃N₄/TiO₂ system was ascribed to the cooperative effects induced by the creation of a heterojunction between TiO₂ and g-C₃N₄ photocatalysts and a subsequent enhancement in optical absorption and charge separation evoked by Cu species and the co-catalytic effect of Ni(OH)₂ toward the oxygen evolution reaction.²⁰² A ternary photoanode of carbon dots (CD)/ultra-thin carbon nitride (UCN) coupled to TiO₂ nanorods with improved PEC activity was fabricated by Kong *et al.*²⁰³ While CDs can significantly facilitate the decomposition of H₂O₂, an

intermediate of two-electron water oxidation, and induce rapid reaction kinetics, UCN efficiently accelerates charge separation and restricts electron/hole recombination. The TiO₂/g-C₃N₄/CNT photoanode with excellent stability and an onset potential of 0.25 V_{Ag/AgCl} has been reported.²⁰⁴ The excellent photochemical performance benefits from the migration of photoinduced electrons from g-C₃N₄ to TiO₂ and their intimate interface contact with CNT. A hierarchical Co₃O₄/P-C₃N₄/TiO₂ photoanode with matched and continuous energy band positions was designed for visible-light-driven PEC water splitting.²⁰⁵ Swift diffusion of the photogenerated holes from the 1-D TiO₂@P-C₃N₄ core-shell structure to the surface of the 0-D Co₃O₄ nanodots and consecutive transfer of the photogenerated electrons to the counter electrode contributes to the high PEC performance. The short diffusion path for holes through highly dispersed 0-D Co₃O₄ nanodots inhibits the accumulation of holes.

A morphology-controlled synthesis of g-C₃N₄/Fe₂O₃ composites resulted in enhanced interfacial charge transfer.²⁰⁶ Small amounts of α -Fe₂O₃ nanosheets are reported to promote the exfoliation of g-C₃N₄, producing a 2D hybrid that exhibits tight interfaces forming a Z-scheme junction.²⁰⁷ Ti⁴⁺ doping of Fe₂O₃ promoted the charge transfer due to enhancement in the conductivity of bulk Fe₂O₃.¹⁰⁴ The electrostatic self-assembly of negatively charged Fe₂O₃ and protonated C₃N₄ forming a Z scheme with hydrogen bond-facilitated charge transfer has been reported.⁹⁶ Aerosol-assisted chemical vapour deposition (AACVD) and the ensuing spin coating and air annealing have been employed for the creation of α -Fe₂O₃/g-C₃N₄ heterojunction photoanode.¹⁶⁷ The unique nanoflake structure of α -Fe₂O₃ promotes good adhesion with g-C₃N₄, leading to strong interfacial contact and lends admirable stability to the photoanode. The intimate contact at the heterojunction facilitates the electron transfer from the CB of g-C₃N₄ towards the less negative CB of α -Fe₂O₃ and hole transfer from the more positive VB of α -Fe₂O₃ to that of g-C₃N₄. The consequent accumulation of electrons in α -Fe₂O₃ and holes in g-C₃N₄ prevents the charge recombination and eventually leads to enhanced PEC performance.²⁰⁸ Integration of the Co-Pi cocatalyst promoted water oxidation, yielding a high photocurrent density.^{209,210} The synthesis of narrow band gap wine-red carbon nitride (WRCN) from carbon-rich supramolecular precursors and the subsequent coupling with Fe₂O₃ forming a type II heterojunction have been attempted.²¹⁰ WRCN showed enhanced absorption extending to the near IR region, probably due to a high degree of polymerisation facilitated by molten salts like NaCl/KCl used in the ionothermal method. High PEC activity of metallic and bimetallic carbon nitride integrated with hematite was reported.^{211,212} The surface modification of a hematite dendrite/g-C₃N₄ composite with an oxidation cocatalyst (CoFeO_x) could achieve enhanced visible-light-induced PEC water splitting.²¹¹ The higher electronic conductivity of the CoFeO_x layer enables effective charge transfer at the electrode/electrolyte interface during water oxidation. The breakage of electro-neutrality and the formation of a tubular structure, depending on the annealing temperature, have been postulated.²¹² The bending of carbon nitride sheets to the tubular structure with



cobalt embedded in the center was proposed to be aided by the Co site. An integrated photoanode constructed with carbon quantum dot (CQD)-sensitized Ti:Fe₂O₃@graphitic carbon nitride nanosheets (GCNNS) core-shell array displayed a photocurrent density of 3.38 mA cm⁻² at 1.23 V_{RHE}.²¹³ Ti³⁺ effectively boosts bulk charge separation, as revealed by the anodic shifting of the flat band potential, while CQDs aid in charge carrier separation and a shift in the onset potential of the photoelectrode due to its inherent capability of H₂O₂ oxidation. Interfacial coordination between C₃N₄ and CdS-Fe₃O₄ promoted the band gap-dependent interfacial charge transfer and contributed to the overall PEC performance of the ternary system.²¹⁴ N-doped carbon dots were anchored on g-C₃N₄/Fe₂O₃ for the degradation of trimethoprim and H₂ evolution from wastewater.²¹⁵

Absorption in the visible region, good electron transport properties, photocorrosion resistance, chemical/thermal stability, and band edges suitable for water splitting render WO₃ a promising material for energy harvesting. g-C₃N₄/WO₃ heterojunction plate array films were synthesised through combinative hydrothermal and dipping-annealing methods.²¹⁶ As-prepared g-C₃N₄/WO₃ heterojunction films achieved a maximum photocurrent density of 2.10 mA cm⁻² at 2 V_{RHE}, almost 3-fold higher than pure WO₃ film. In the heterojunction film, the photo-generated electrons of g-C₃N₄ easily migrate to the CB of WO₃ and then to the FTO substrate and reach the counter electrode through the external circuit. Similarly, the photo-generated holes of WO₃ transferred to the VB of g-C₃N₄ can take part in the oxygen evolution reaction.²¹⁶⁻²¹⁸ The substantial stability of WO₃/g-C₃N₄ nanosheet photoanodes after continuous illumination for 3600 seconds, and efficiency for seawater splitting have also been reported.²¹⁷ The order of the deposition clearly influenced the type of heterojunction formed and significantly affected the PEC performance.⁸¹ The Z-scheme g-C₃N₄/NCDs/WO_x photocatalyst, where nitrogen-doped carbon dots (NCDs) acted as the electron mediator, exhibited an apparent quantum efficiency of 7.58% at 420 nm.⁹⁷ The localised surface plasmon resonance effect of WO_x and the photoluminescence property of NCDs enhanced the NIR utilisation efficiency. Nanobelt-like WO_x overlapped with NCDs on the surface of CN nanosheets and the close solid-solid interface ensured the fast charge mobility.

ZnO/C₃N₄ type II heterojunctions have been explored for their photoelectrochemical performance.²¹⁹⁻²²³ The surface deposition of g-C₃N₄ on ZnO nanowires/nanorods with smooth and rapid interfacial electron transfer has been attempted. The incorporation of Pt clusters formed a ternary photoanode generating a photocurrent density of 120 μA cm⁻² at 0.5 V_{Ag/AgCl} in a 0.5 M Na₂SO₄ solution.²¹⁹ Both g-C₃N₄ and ZnO acted as light absorbers while Pt nanoclusters served as the cocatalyst facilitating the transfer of the photogenerated electrons. Sulphuration of the ZnO electrode could form core-shell ZnO/ZnS heterostructures, which were further integrated with C₃N₄ to obtain ternary photoanodes with enhanced PEC performance.²²¹ The sulphurisation process occurs *via* anion exchange through which surface trap states such as oxygen vacancies and adsorbed oxygen of

pristine ZnO nanorods become further reduced to form the ZnS interlayer. Type II photoanodes were designed by coating PCN films onto highly conductive yttrium (Y)-doped zinc oxide (ZnO) nanorods (NRs) serving as charge collectors.¹⁰⁰ Bifunctional CoPi efficiently inhibited the photocorrosion of g-C₃N₄/ZnO and provided a hole transfer channel.²²⁴ Further, the Fermi level potential of g-C₃N₄@ZnO shifted towards the positive direction with a resultant upward band-bending at the band edge position, promoting the separation efficiency of the photogenerated electron-hole pairs.²²⁵ CdS quantum dots modified g-C₃N₄/ZnO nanorods core-shell structures were fabricated *via* hydrothermal and SILAR (successive ionic layer adsorption and desorption) processes. The photogenerated electrons in g-C₃N₄ and CdS were transported to ZnO and the Pt electrode for the HER.²²⁶ Masoumi *et al.* constructed a dual heterojunction of ZnO with Fe₂O₃ and g-C₃N₄, which facilitated electron-hole separation to the surface of the substrate, thereby increasing the PEC performance.²²⁷

SnO₂ is one of the most investigated wide band gap materials for energy-harvesting applications. SnO_{2-x}/g-C₃N₄ heterojunction nanocomposites were prepared by a convenient one-step pyrolysis method.¹⁰³ Ultrasonication ensures the homogenisation of Sn(OH)₄ with melamine due to the formation of hydrogen bonds; during the thermal treatment, melamine decomposes into g-C₃N₄, releasing reducing gases such as NH₃, with the consequent formation of SnO_{2-x}. This has been reported to enhance charge-carrier mobility, and visible-light absorption capability is achieved due to the presence of oxygen vacancies in nonstoichiometric (reduced) semiconductor nanocrystals. The homogeneous deposition of g-C₃N₄ nanodots in amorphous mesoporous 1D SnO₂ as the host *via* pulsed electrophoresis followed by water soaking treatment to crystallize amorphous SnO₂ could yield extended visible light absorption and deliver a photocurrent density of 1.8 mA cm⁻² at 0.2 V_{Ag/AgCl}.²²⁸ Incorporating plasmonic Au into the SnO₂ quantum dots (SQD) improved the performance by providing a pathway for the transportation of electrons from g-C₃N₄ to SQD.²²⁹ The band-bending strategy effectively separates the electron-hole pair, thereby improving the PEC performance.

p-type NiO exhibits strong resistance to photo-corrosion in neutral electrolyte solutions. It shows perfect lattice matching with g-C₃N₄ and possesses a compatible band alignment, enabling the formation of a type II heterojunction. The more positive VB potential of NiO enables the injection of photo-generated holes from g-C₃N₄ to NiO, suppressing the charge-recombination by effectively passivating the surface-trapped electrons. A 2D/2D interface between Ni/NiO hexagonal nanosheets and g-C₃N₄ *via in situ* solid-state heat treatment exhibited superior activity for electrochemical and photoelectrochemical water splitting.²³⁰ The use of a liquid-phase laser ablation technique for the heterostructured nanocomposite NiO@g-C₃N₄ has been reported.²³¹

3.1.4 Tungstates and vanadates. Bi₂WO₆ QDs coupled with g-C₃N₄ form a Z scheme and the one-step hydrothermal synthesis mediated by oleate ions prevented the aggregation of Bi₂WO₆ QDs.²³² A type II heterojunction of S-doped g-C₃N₄/Bi₃WO₆ was fabricated from an ultrasonication approach to



overcome the sluggish charge transfer at the electrode/electrolyte interface and fast recombination of electron-hole pairs of Bi_2WO_6 (BWO).²³³ It has been speculated that in S-doped $g\text{-C}_3\text{N}_4$ (SCN), the VBM is located on N atoms except for the N atom near sulfur, while CBM is mainly located on the S atom at the adjacent heptazine unit. This enhances the photogenerated electron-hole pair separation, reducing recombination and enhancing the photocatalytic efficiency.²³⁴ The electron migration process generates the positively charged electron depletion layer in SCN near the interface, which leads to the upward bending of the band edge. Similarly, an electron accumulation layer in the BWO near the interface causes the downward bending of the band edge in BWO. The resultant inner electric field (IEF) at the interface resists further electron transfer. The energy level positioning favours the formation of a type II heterojunction with facile electron transfer. A 2D/1D heterostructure with ZnWO_4 nanorods decorated over the $g\text{-C}_3\text{N}_4$ nanosheets ($g\text{-C}_3\text{N}_4/\text{ZnWO}_4$) was successfully fabricated by hydrothermal synthesis.²³⁵ The band gap modification was attributed to the band bending arising due to heterojunction formation.

BiVO_4 has been well explored as a photocatalyst and photoelectrocatalyst due to its visible light sensitivity, band edge positions suitable for hydrogen evolution and high stability. A Z-scheme mechanism at the $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ interface has been well established.^{236,237} The relative band positions induce the injection of excited electrons on the CB of BiVO_4 into the VB of $g\text{-C}_3\text{N}_4$ to recombine with photogenerated holes and restrain recombination. The CB of $g\text{-C}_3\text{N}_4$ and the VB of BiVO_4 were projected as the centres for reduction and oxidation, respectively. Uniform films with good coverage and crack-free surfaces could be obtained by electrospinning and the nanostructured heterojunction facilitated the electron-hole separation due to a shorter charge transport distance with a consequent high photocurrent density and negative shift of onset potential.¹¹⁴ The augmented activity of $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ microflower structures has been reported.²³⁸ $g\text{-C}_3\text{N}_4$ nanolayers self-assembled with BiVO_4 into a highly coupled $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ dyad augmented the charge separation efficiency of the BiVO_4 photoelectrodes for the OER.²³⁹ The incident photon-to-current conversion efficiency (IPCE) provided by the scalable $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ photoanodes was estimated to be 50% at 1.23 V_{RHE} in 0.5 M Na_2SO_4 solution and significantly increased to 97% at an applied voltage of 1.6 V_{RHE} . The enhanced visible light absorption of the dyads was attributed to the multiple reflections of light rays in the hierarchical structure attained by the introduction of $g\text{-C}_3\text{N}_4$ nanolayers. The $g\text{-C}_3\text{N}_4$ nanolayers function as the pump to extract electrons from the BiVO_4 side for better OER performance, with the pumping effect being enhanced by the bias voltage. Ultrathin $g\text{-C}_3\text{N}_4$ nanosheets were projected as an efficient metal-free cocatalyst for improving the oxygen evolution activity of the nanoporous BiVO_4 photoanode.^{240,241} Fig. 7 represents the illustration of the exfoliation/acidification process for fabricating $\text{BiVO}_4/g\text{-C}_3\text{N}_4\text{-NS}$ photoanodes with enhanced PEC performance. The $g\text{-C}_3\text{N}_4$ nanolayers not only suppress the surface charge recombination of BiVO_4 but also effectively accommodate

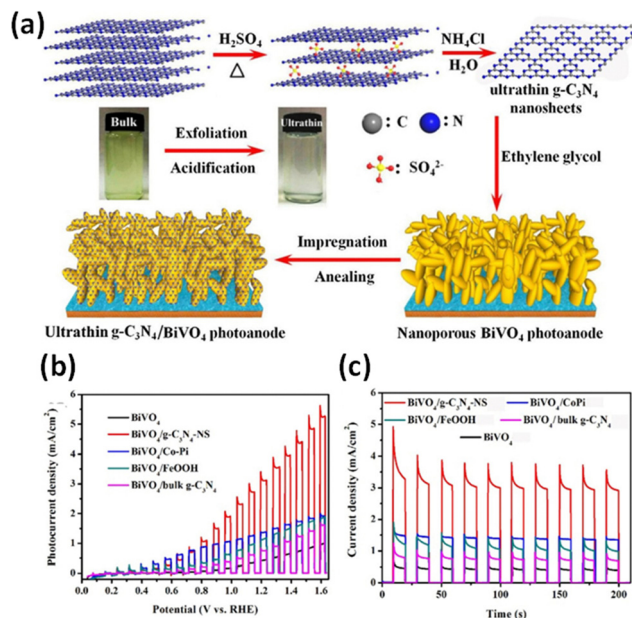


Fig. 7 (a) Schematic illustration of the exfoliation and acidification process for the fabrication of $\text{BiVO}_4/g\text{-C}_3\text{N}_4\text{-NS}$ photoanodes. Reprinted from ref. 240 with permission. (b) J - V curves, (c) transient photocurrent response (1.23 V vs. RHE) for different photoanodes measured under visible-light illumination in 0.1 M Na_2SO_4 . Reprinted from ref. 242 with permission.

photogenerated holes in the VB for water oxidation. Mo doping of BiVO_4 enhances the charge separation due to exceptional electron transfer capability.^{239,240} Mo doping significantly reduces the interfacial energy loss *via* work function adjustment and increases the open circuit photovoltage of BiVO_4 .²⁴² A similar effect is generated at the $g\text{-C}_3\text{N}_4$ interface rendering an IPCE of 2.67% at 0.54 V_{RHE} for the $g\text{-C}_3\text{N}_4/\text{Mo-BiVO}_4$ heterojunction. The inclusion of NiFeO_x as an oxygen evolution catalyst greatly improves the PEC performance. The DFT simulations proposed the separation of electron/hole pairs facilitated by the creation of an internal electric field at the $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ interface *via* the formation of a van der Waals-type heterojunction.¹⁰⁵ A combined theoretical/experimental approach was adopted by Mohamed *et al.* to establish the boosted performance of the γ -irradiated $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ heterojunction.²⁴³ γ irradiation was observed to alter the surface topology and the enhancement in optical properties was attributed to the hybridisation of C 1s and N 1s. A combined theoretical and experimental study was conducted on the $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ heterojunction synthesised by a modified sol-gel technique by varying the weight ratios of $g\text{-C}_3\text{N}_4$.²⁴⁴ A comparative evaluation of the impact of carbon nanotubes, reduced graphene oxide and graphitic carbon nitride in enhancing the PEC performance of BiVO_4 has been attempted and the maximum IPCE was reported for the $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ heterojunction.²⁴⁵ The band bending at the nano junction was estimated to reduce bulk recombination and facilitate charge transport and transfer. The boosted PEC performance could be correlated to efficient charge transfer kinetics as a result of the increased number of charge carriers and the lowering of the



charge transfer resistance. Samsudin *et al.* reported the augmented photoelectrocatalytic performance of the $g\text{-C}_3\text{N}_4/\text{BiVO}_4$ micro-flower composites with supporting theoretical studies.²³⁸ The photocatalytic and photoelectrochemical performances of $g\text{-C}_3\text{N}_4/\text{InVO}_4$ ²⁴⁶ and $\text{FeVO}_4/g\text{-C}_3\text{N}_4$ ²⁴⁷ systems have also been reported.

3.1.5 Chalcogenides. The outstanding mechanical and electrical properties of molybdenum disulfide (MoS_2) with a 2D layered structure attracted much attention and it has been extensively explored as a hydrogen evolution catalyst.²⁴⁸ Metallic MoS_2 loaded on $g\text{-C}_3\text{N}_4$ showed an enhancement in PEC performance and photochemical H_2O_2 generation.²⁴⁹ The layered MoS_2 co-catalysts were distributed on the surface of $g\text{-C}_3\text{N}_4$ *via* a facile impregnation method and the formation of intimate interfaces facilitated charge transfer and visible light sensitivity.²⁵⁰ The interfacial transfer of photogenerated electrons in the CB of $g\text{-C}_3\text{N}_4$ to MoS_2 renders the conduction band electrons more mobile, enabling the separation of electron-hole pairs. The hydrothermal growth of MoS_2 over the S-doped $g\text{-C}_3\text{N}_4$ deposited *via* CVD on the ITO substrate formed a p-n junction with high PEC performance due to the synergistic effect arising from high charge carrier concentration, efficient charge separation and enhanced light absorption.²⁵¹ Ye *et al.* reported an n-n type heterojunction with a typical type II band structure.²⁵²

Plasmonic Bi nanoparticles supported over a $g\text{-C}_3\text{N}_4/\text{Bi}_2\text{S}_3$ photoanode for PEC water splitting were reported by Subramanyam *et al.*²⁵³ Decoration of Bi_2S_3 QDs on $g\text{-C}_3\text{N}_4$ extended the absorption edge to the near-infrared region and it was further enhanced by the plasmonic effect of Bi nanoparticles. The maximum photocurrent at around 310 nm could be attributed to the formation of energetic hot electrons, and the presence of Bi nanoparticles accelerated the overall charge transportation, resulting in PEC-driven hydrogen generation. The intimate $\text{In}_2\text{S}_3/g\text{-C}_3\text{N}_4$ interface promoted charge transfer and inhibited the recombination of electron-hole pairs, significantly improving the PEC performance.^{254,255} The highly conductive In_2S_3 rapidly withdraws electrons from $g\text{-C}_3\text{N}_4$, transferring them to ITO. Meanwhile, the photogenerated holes in the $g\text{-C}_3\text{N}_4$ nanosheets are transferred to In_2S_3 NPs and are consumed at the $\text{In}_2\text{S}_3/g\text{-C}_3\text{N}_4$ -electrolyte junction. The PEC activity and stability were greatly enhanced by combining CdS and $g\text{-C}_3\text{N}_4$ through the formation of an interlocking thin film, which provided a large contact area and better adhesion to FTO.²⁵⁶ Due to the higher positioning of the VB and CB of C_3N_4 relative to CdS, the photoexcited electrons of $g\text{-C}_3\text{N}_4$ were directly transferred to CdS, and the holes in the valence band of CdS migrated to the conduction band of $g\text{-C}_3\text{N}_4$. The $\text{Ag}@g\text{-C}_3\text{N}_4/\text{ZnS}$ photoanode with a photocurrent turn-on potential of $0.45 V_{\text{RHE}}$ has been reported.²⁵⁷ The light passed through the transparent ZnS layer to $\text{Ag}@g\text{-C}_3\text{N}_4$ and then to TiO_2 , an electron-selective layer, which enhanced the transfer of electrons to the circuit while the incorporation of $\text{Ni}(\text{OH})_2$ improved the stability of the photoanode and its water oxidation capability. Chaudhary *et al.* reported the synthesis of copper sulphide (CuS) supported on Ni-incorporated graphitic carbon nitride sheets. The improved activity was assigned to the band bending induced

by the larger space region width, the formation of an effective p-n junction between CuS and $g\text{-C}_3\text{N}_4$ lowering the effective band gap, and the facile charge transfer kinetics due to Ni incorporation into the $g\text{-C}_3\text{N}_4$ matrix.¹⁶⁴ The conceptual design of the $\text{InSe}/g\text{-C}_3\text{N}_4$ van der Waals heterostructure with type II band alignment to achieve spontaneous and highly efficient water splitting was proposed by He *et al.*²⁵⁸

3.1.6 Layered double hydroxides (LDH). The special interest in layered double hydroxides (LDH) in catalysis can be traced to their lamellar structure, redox properties, non-toxicity, and high structural stability. The formation of oxo-bridges facilitates the metal-to-metal charge transfer, thereby decelerating the electron-hole recombination.^{259,260} The *in situ* assembly of N-deficient porous carbon nitride nanosheets and the NiFe-layered double hydroxide into a 3D N-doped graphene framework was attempted by Hou *et al.* to obtain a 3D hierarchical nanostructure.²⁶¹ The ternary hybrid exhibited remarkable photoelectrochemical performance for water oxidation, which was attributed to the effectual light trapping, multidimensional electron transport trails, rapid charge transport, strong coupling effect and amended surface reaction kinetics. CoMn-LDH ²⁶² and CoFe-LDH ²⁶³ coupled with $g\text{-C}_3\text{N}_4$ for high photoelectrochemical performance have been reported.²⁶² NiCo-LDH was introduced onto $g\text{-C}_3\text{N}_4$ film through cathodic electrochemical deposition and acted as a co-catalyst for water oxidation.²⁶⁴ N-doped graphene, introduced into the heterostructure assembly of the $g\text{-C}_3\text{N}_4/\text{NiFe-LDH}$ hybrid behaves as an electronic mediator to strengthen the interfacial interactions and charge transfer.²⁶⁵ A Z-scheme charge transfer mechanism due to enriched oxygen vacancy defects in NiFe-LDH and N-r-GO contributes to the superior photoactivity of the heterostructure. The ruptured tubular structure of graphitic carbon nitride (RT $g\text{-C}_3\text{N}_4$) was reported to improve charge separation.⁸⁵ Efficient photoelectrochemical water oxidation proceeded over the $\text{CuTi-LDH}/g\text{-C}_3\text{N}_4$ type II heterojunction.²⁶⁶ Bismuth oxycarbonate ($\text{Bi}_2\text{O}_2\text{CO}_3$) grafted NiFe LDH on $g\text{-C}_3\text{N}_4$. Interfacial electron transfer aiding photoelectrochemical water splitting *via* the S-scheme mechanism has also been demonstrated.²⁶⁷

3.1.7 Miscellaneous. Samanta *et al.* reported the plasmonic enhancement of H_2 evolution over $\text{Au}/\text{C}_3\text{N}_4$ systems.¹²¹ The induced plasmonic resonance of Au NPs augmented the electron passage through the Schottky barrier at the $\text{Au}/g\text{-C}_3\text{N}_4$ interfaces and the accumulation of many electrons in the CB leads to high photocurrent and H_2 evolution. A hierarchical core-shell copper-azolate- C_3N_4 framework (CuAF) integrated with $\text{Ni}(\text{OH})_2$ as the cocatalyst forming a staggered-gap type II heterojunction for water oxidation was constructed by Karimi-Nazazbad *et al.*²⁶⁸ The relative positioning of the valence and conduction bands in the heterojunction resulted in the accumulation of electrons and holes in the CB of C_3N_4 and valence band of CuAF, respectively. The construction of a photoanode by loading 2D crystallised $\text{Ni}(\text{OH})_2$ on the surface of three-dimensionally microporous $g\text{-C}_3\text{N}_4$ *via* an electrostatic method was demonstrated by Cao *et al.*²⁶⁹ The resultant Z scheme heterojunction accelerated the charge carrier separation while the 2D/3D hollow structure facilitated their diffusion.



Bismuth oxyhalides are characterised by distinctive layer structures and narrow band gaps, rendering them suitable for photocatalytic and photoelectrocatalytic applications. The $g\text{-C}_3\text{N}_4/\text{BiOF}$ heterojunction was synthesised using an ultrasonication process and explored as photoanode material in PEC water splitting.²⁷⁰ Under light illumination, the photoinduced electrons were transferred to the CB of BiOF from the CB of $g\text{-C}_3\text{N}_4$. Simultaneously, the holes moved from the VB of BiOF toward the VB of $g\text{-C}_3\text{N}_4$. The optimized 6% $g\text{-C}_3\text{N}_4/\text{BiOF}$ electrode showed excellent photoelectrochemical water splitting performance with wastewater rejected from reverse osmosis. The improved PEC performances of $g\text{-C}_3\text{N}_4/\text{BiOI}$ ^{95,98,271,272} and BiOBr ¹⁶³ as photoanode materials were investigated. The synergistic trap passivation and charge separation at the $g\text{-C}_3\text{N}_4\text{-S}/\text{BiOI}$ heterojunction resulted in a higher photocurrent because of lower charge transfer resistance.⁹⁸ The exfoliation *via* the breakage of hydrogen bonds between the sheets and increased crystallinity led to better charge transportation. The integration of Ni as a cocatalyst into the $g\text{-C}_3\text{N}_4$ framework enhanced the photocurrent density by minimising the activation energy barrier and enhancing the charge separation and transportation.¹⁶³ The introduction of dopant ions (Nd^{3+}) influenced the microstructural, optical and photoelectrochemical properties of C_3N_4 and the heterojunction with BiOI showed considerable improvement in the PEC water splitting performance.²⁷³

Ultrathin $g\text{-C}_3\text{N}_4$ nanolayers were used as the co-catalyst to boost the OER of Bi_2MoO_6 nanosheet arrays with exposed (010) facets.²⁷⁴ The high surface area, exposed oxygen atoms and even electron transport pathways facilitate charge separation resulting in enhanced PEC performance. Li *et al.* demonstrated the fabrication of a direct Z-scheme heterojunction by encapsulation of the $\text{Bi}_2\text{O}_3/\text{BiPO}_4$ p-n junction in the $g\text{-C}_3\text{N}_4$ framework.²⁷⁵ A new perception of interface engineering was attempted by introducing the nuclear fuel ThO_2 onto $g\text{-C}_3\text{N}_4$ for the water-splitting application. The presence of thorium nitrate during $g\text{-C}_3\text{N}_4$ polymerisation altered the structure and morphology, improving the PEC stability of the photoanode.²⁷⁶ Zheng *et al.* reported a plasma-assisted liquid-based fabrication of the $g\text{-C}_3\text{N}_4/\text{Mn}_2\text{O}_3$ p-n heterojunction, which led to the accumulation of electrons and holes in the VB of $g\text{-C}_3\text{N}_4$ and CB of Mn_2O_3 , respectively.²⁷⁷ Ag-Ni alloy particles were homogeneously distributed throughout the $g\text{-C}_3\text{N}_4$ matrix using an *in situ* solid-state heat treatment, as evidenced by the TEM images. This was the first demonstration of the efficient tuning of the photoelectrochemical properties of $g\text{-C}_3\text{N}_4$ photoanodes by incorporating bimetallic alloy particles.²⁷⁸

Chen *et al.* synthesised a vertically aligned Si nanowire (NW)/ $g\text{-C}_3\text{N}_4$ core-shell array using metal-catalysed electroless etching, liquid atomic layer deposition, and annealing methods. The photoelectrode exhibited an extended optical absorption range and significantly improved the PEC performance in comparison with the bulk phase $g\text{-C}_3\text{N}_4$.²⁷⁹ Enhanced visible light absorbance and reduced photogenerated charge recombination in $g\text{-C}_3\text{N}_4/\text{SiC}$ synthesised *via* pulsed laser ablation in liquid was evidenced by absorption and photoluminescence spectra and this contributed to the improved photoelectrochemical activity of

the $g\text{-C}_3\text{N}_4/\text{SiC}$ -based photoanode.²⁸⁰ A direct Z-scheme $\text{NiTiO}_3/g\text{-C}_3\text{N}_4$ heterojunction with enhanced activity under white LED activation was assembled by a simple calcination method.²⁸¹ Polydisperse cobalt phosphide nanoparticles were deposited over $g\text{-C}_3\text{N}_4$ to form a CoP-CN heterostructure with strong intimate interfacial contact, charge transfer efficiency and stronger photo-reductive capability.^{282,283} A synergistic effect between the Pt nanoparticles and CoP over the $g\text{-C}_3\text{N}_4$ nanosheets contributed to highly boosted photo/electrochemical activity.²⁸³ Islam *et al.* demonstrated the superior performance and stability of the thermolytically fabricated $g\text{-C}_3\text{N}_4/\text{ZnGa}_{1.9}\text{Al}_{0.1}\text{O}_4$ heterojunction as compared to a hydrolytically prepared counterpart.²⁸⁴ A nano-engineering approach to the construction of an integrated 3D photoanode comprised of a 1D/2D Ba-doped TaON array and 2-D $g\text{-C}_3\text{N}_4$ nanosheets decorated with CoO_x nanoparticles by an innovative stack design, generating a photocurrent of 4.57 mA cm^{-2} at $1.23 V_{\text{RHE}}$ under AM 1.5 simulated sunlight, has been proposed.²⁸⁵ Table 1 presents a concise comparative evaluation of the PEC performance of $g\text{-C}_3\text{N}_4$ -based photoanodes.

3.2 Graphitic carbon nitride and its composites as photocathodes

Investigations on photocathodes are rather limited and the most explored systems include Cu_2O ,^{124,286,287} and CuO .^{118,288,289} Cu_2O is a typical p-type narrow band gap ($\sim 2 \text{ eV}$) semiconductor with a theoretical photocurrent of -14.7 mA cm^{-2} for water splitting and a solar to hydrogen conversion efficiency of 18.1% on the AM 1.5 spectrum.²⁹⁰ Due to specific band alignments at an effective heterojunction, the photoexcited electrons in the CB of Cu_2O can transfer to the CB of $g\text{-C}_3\text{N}_4$ while the photoexcited holes can transfer from the VB of $g\text{-C}_3\text{N}_4$ to the VB of Cu_2O . The PEC performance graphs and schematic pathway for photo-electron excitation and transfer in the $\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4$ under visible light irradiation are depicted in Fig. 8.¹²⁴ The efficiency and stability of the Cu_2O foam photoelectrode could be enhanced by combining it with $g\text{-C}_3\text{N}_4$ as a protection layer to alleviate the photocorrosion.²⁸⁷ With the tactical combination of type II band edge heterojunctions and passivation using $g\text{-C}_3\text{N}_4$, a photocathode ($\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4/\text{CoS}$) with high stability was fabricated by Kunturu *et al.*²⁹¹ The enhanced light-to-electricity conversion efficiency of the $\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4$ p-n junction was also utilised to form a triple-layer photocathode $\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4/\text{WS}_2$.²⁸⁶ The mixed-phase WS_2 nanosheets obtained *via* Li intercalation served as an operative hydrogen evolution catalyst along with enacting the function of an electron acceptor to facilitate electron-hole separation.

A 3D hierarchical C-doped $\text{CuO}/g\text{-C}_3\text{N}_4$ nanocomposite synthesised by a facile *in situ* microwave-assisted one-pot process yielded CuO nanosheets assembled into unique micro-flower/dandelion morphologies.²⁸⁸ High photocorrosion stability, extensive visible light absorption, and excellent PEC performance by $\text{CuO}/g\text{-C}_3\text{N}_4$ nanocomposites, aided by efficient charge segregation and transfer at the electrode-electrolyte interface and high surface area, have been reported.^{118,288,289}

Visible light-aided hydrogen production by PEC water splitting was successfully achieved by the direct synthesis of $g\text{-C}_3\text{N}_4$



Table 1 PEC performance of g-C₃N₄-based photoanodes

| System | Photocurrent density (mA cm ⁻²) | Potential | Electrolyte | Ref. |
|--|---|---------------------------|--|------|
| BCN-0.6 | 0.055 | 1.23 V _{RHE} | 0.2 M Na ₂ SO ₄ + 0.05 M Na ₂ S | 72 |
| Ph-CN ₆₀₀ | 0.06 | V _{Ag/AgCl} | 0.1 M KOH | 73 |
| Ag/g-C ₃ N ₄ (1 : 10) | 0.00640 | V _{SCE} | 0.05 M Na ₂ SO ₄ | 74 |
| Ni-CN _x | 0.0698 | 0.26 V _{Ag/AgCl} | 0.1 M KOH | 75 |
| WO ₃ /g-C ₃ N ₄ | 0.82 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 81 |
| Co-g-CN | 3.253 | V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 84 |
| BiOI/g-C ₃ N ₄ | 0.0815 | V _{Ag/AgCl} | 1 M KOH | 95 |
| g-C ₃ N ₄ -S/BiOI | 0.70 | V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 98 |
| 0.8%Y:ZnO@PCN | 0.4 | 1.23 V _{RHE} | Na ₂ SO ₄ | 100 |
| g-C ₃ N ₄ | 0.0014 | V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 101 |
| SCN-27.4 | 0.468 | 0.6 V _{Ag/AgCl} | 0.2 M Na ₂ SO ₄ | 102 |
| Ti ³⁺ -TiO ₂ /O-g-C ₃ N ₄ | 0.0034 | V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 103 |
| 0.5 g-C ₃ N ₄ /Ti-Fe ₂ O ₃ | 2.55 | V _{Ag/AgCl} | 1 M NaOH | 104 |
| g-C ₃ N ₄ /BiVO ₄ | 0.42 | V _{RHE} | 0.5 M Na ₂ SO ₄ | 105 |
| C _{PVP} /g-C ₃ N ₄ | 0.00664 | V _{SCE} | 0.5 M Na ₂ SO ₄ | 113 |
| CN/BV-1 | 0.44 | 0.56 V _{RHE} | 0.5 M PBS + Na ₂ SO ₃ | 114 |
| CN-rGO _{0.5} | 0.072 | 1.23 V _{RHE} | 0.1 M KOH | 116 |
| g-CN600 | 0.12 | 1.55 V _{RHE} | 0.1 M Na ₂ SO ₄ + 0.1 M Na ₂ SO ₃ + 0.01 M Na ₂ S | 129 |
| g-CN | 0.062 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 130 |
| CMD5 | 0.1 | 1.55 V _{RHE} | 0.1 M Na ₂ SO ₄ + 0.1 M Na ₂ SO ₃ + 0.01 M Na ₂ S | 131 |
| g-CN400 | 0.075 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ + 0.1 M Na ₂ SO ₃ + 0.01 M Na ₂ S | 132 |
| g-C ₃ N ₄ | 0.089 | 1.1 V _{RHE} | 0.1 M Na ₂ SO ₄ | 133 |
| TiO ₂ /CMB | 1.4 | V _{Ag/AgCl} | 0.1 M Na ₂ S | 134 |
| S-BCN | 0.1032 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 137 |
| CN@FTO | 0.030 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 144 |
| CN-h | 0.0035 | 0.6 V _{SCE} | 0.2 M Na ₂ SO ₄ | 147 |
| CN | 0.116 | 1.23 V _{RHE} | 0.1 M KOH | 151 |
| Exfoliated g-C ₃ N ₄ | 0.01021 | V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 152 |
| CN _T | 0.266 | 1.23 V _{RHE} | 0.1 M KOH | 153 |
| g-CN PNR | 0.1205 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 154 |
| PCN | 0.100 | 1.23 V _{RHE} | 1 M NaOH | 155 |
| 1D-S-C ₃ N ₄ | 0.010 | 1 V _{SCE} | 0.1 M Na ₂ SO ₄ | 157 |
| Co/S-C ₃ N ₄ /BiOCl | 0.393 | 1.23 V _{RHE} | 0.5 M KCl + KH ₂ PO ₄ | 158 |
| P-C ₃ N ₄ /TiO ₂ | 1.98 | 0 V _{Ag/AgCl} | 1 M NaOH | 159 |
| BCN/TiO ₂ | 1.01 | 1.23 V _{RHE} | 1 M NaOH | 160 |
| CN/BCN | 0.62 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 161 |
| Ni/S-gC ₃ N ₄ /BiOBr | 0.177 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₃ + NaHCO ₃ | 163 |
| Ni/g-C ₃ N ₄ @CuS | 15.5 | V _{RHE} | 0.1 M KOH | 164 |
| Bi@g-C ₃ N ₄ /GO | 0.3 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 165 |
| P/g-C ₃ N ₄ | 0.00025 | 1.2 V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 166 |
| V doped g-C ₃ N ₄ | 0.80 | V _{RHE} | 0.1 M KOH | 167 |
| TiO ₂ @Co-C ₃ N ₄ | 1.79 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 168 |
| Pd@g-C ₃ N ₄ | 0.0788 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 169 |
| GCNML | 0.12 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 171 |
| CN-CNT | 0.075 | 1 V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 174 |
| pCN/C dots | 0.038 | 1 V _{RHE} | 5% v/v TEOA + 0.5 M Na ₂ SO ₄ | 175 |
| TiO ₂ /C ₃ N ₄ -CMT | 2.74 | 1.23 V _{RHE} | NaOH | 176 |
| CT _{5,0} | 1.481 | V _{Ag/AgCl} | 0.5 M Na ₂ S | 179 |
| C ₃ N ₄ -TiO ₂ | 1.5 | V _{RHE} | 0.25 M Na ₂ S + 0.35 M Na ₂ SO ₃ | 180 |
| PCN-TNA | 1.42 | 1.23 V _{RHE} | 0.2 M Na ₂ SO ₃ | 181 |
| TNT-L | 0.87 | 0 V _{Ag/AgCl} | 1 M KOH | 182 |
| g-C ₃ N ₄ /TNTAS | 0.86 | 0.7 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 184 |
| TiO ₂ -4 h/g-CN | 0.0433 | 0.6 V _{SCE} | 0.2 M Na ₂ SO ₄ | 185 |
| 20-gCN@TiO ₂ | 0.0723 | 1.23 V _{RHE} | 1 M KOH | 186 |
| 0D/1D g-C ₃ N ₄ /0 V-TiO ₂ | 0.72 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 187 |
| CN QDs/TiO ₂ | 1.34 | 0.3 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 188 |
| g-C ₃ N ₄ QDs/TNTAs | 0.62 | 0.6 V _{SCE} | 0.1 M Na ₂ SO ₄ | 189 |
| CNB _{0.15} QD@TiO ₂ | 0.57 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 190 |
| d-FCNs ^{-21.59} /TiO ₂ | 0.1219 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 192 |
| g-C ₃ N ₄ /TiO ₂ | 0.1427 | 1.23 V _{RHE} | 1 M KOH | 193 |
| TNR@C _N -C ₃ N ₄ /FTO | 0.64 | 1.5 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 194 |
| g-C ₃ N ₄ /TNAs | 0.206 | 0.63 V _{RHE} | 1 M Na ₂ SO ₄ | 195 |
| CNT70 | 9.33 mA | 1.49 V _{Ag/AgCl} | 1 M Na ₂ SO ₄ | 196 |
| 2D-B-CN-4 | 1.63 | V _{RHE} | 0.1 M Na ₂ SO ₄ | 197 |
| CNF;TNR-4h | 0.18 | 0.6 V _{Ag/AgCl} | 0.1 M KOH | 198 |
| g-C ₃ N ₄ @TiO ₂ @Co-Pi | 1.6 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 199 |
| g-C ₃ N ₄ /TiO ₂ /Co-Pi | 0.346 | 1.1 V _{RHE} | 0.1 M Na ₂ SO ₄ | 200 |
| TiO ₂ @Co-C ₃ N ₄ | 1.79 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 201 |
| TiO ₂ /CuNi@g-C ₃ N ₄ | 0.890 | 1.5 V _{RHE} | 1 M NaOH | 202 |
| CDS/UNC/TiO ₂ | 1.43 | 1.23 V _{RHE} | 1 M NaOH | 203 |



Table 1 (continued)

| System | Photocurrent density (mA cm ⁻²) | Potential | Electrolyte | Ref. |
|--|---|---------------------------|---|------|
| TiO ₂ /C ₃ N ₄ /CNT | 2.94 | 0.6 V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 204 |
| CPCT2 | 1.58 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 205 |
| g-C ₃ N ₄ /Fe ₂ O ₃ | 0.78 | V _{Ag/AgCl} | 1 M NaOH | 206 |
| Fe ₂ O ₃ /R-CN/Co-Pi | 0.7 | 1.23 V _{RHE} | 1 M NaOH | 208 |
| WRCN/hematite/Co-Pi | 2.14 | 1.23 V _{RHE} | 1 M NaOH | 209 |
| CoFeO _x /HD-CN | 0.60 | 1.23 V _{RHE} | 0.1 M NaOH | 210 |
| CoNi-tC ₃ N ₄ /a-Fe ₂ O ₃ | 2.73 | 1.23 V _{RHE} | 1 M NaOH | 212 |
| Ti:Fe ₂ O ₃ @GCNNs | 2.75 | 1.23 V _{RHE} | 0.1 M KOH | 213 |
| Gcnscf | 0.0238 | V _{Ag/AgCl} | Na ₂ SO ₄ | 214 |
| NCD@CNFO | 3.07 | V _{RHE} | 0.1 M Na ₂ SO ₄ | 215 |
| g-C ₃ N ₄ /WO ₃ | 1.48 | 2 V _{RHE} | 0.2 M Na ₂ SO ₄ | 216 |
| WO ₃ /g-C ₃ N ₄ NSAs | 0.73 | 1.23 V _{RHE} | Seawater | 217 |
| g-C ₃ N ₄ /WO ₃ | 1.92 | 1.23 V _{RHE} | 0.1 M KH ₂ PO ₄ | 218 |
| g-C ₃ N ₄ /Pt/ZnO | 0.120 | 0.5 V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 219 |
| 1 D ZnO/g-C ₃ N ₄ | 0.12 | V _{RHE} | 0.5 M Na ₂ SO ₄ | 220 |
| ZnO/ZnS/g-C ₃ N ₄ | 0.66 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 221 |
| ZnO/g-C ₃ N ₄ | 0.25 | 1.23 V _{RHE} | 1 M KOH | 222 |
| ZnO/C ₃ N ₄ -10 | 1.68 | 1.19 V _{RHE} | 0.5 M Na ₂ SO ₄ | 223 |
| Co-Pi/CNNs/ZnO | 2.45 | 1.23 V _{RHE} | 0.2 M Na ₂ SO ₄ | 224 |
| Co-Pi/g-C ₃ N ₄ @ZnO | 5 | 1.23 V _{RHE} | 3.5 wt% NaCl | 225 |
| CdS/g-C ₃ N ₄ /ZnO | 3.34 | 1.23 V _{RHE} | 0.1 M Na ₂ S + 0.2 M Na ₂ SO ₃ | 226 |
| ZnO/α-Fe ₂ O ₃ /g-C ₃ N ₄ | 0.97 | 1.23 V _{RHE} | 1 M NaOH | 227 |
| g-C ₃ N ₄ /SnO ₂ | 1.82 | 0.2 V _{Ag/AgCl} | 0.1 M NaOH | 228 |
| CNAs-20 | 3.93 | 1 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 229 |
| g-C ₃ N ₄ @1/8NiO | 20.0 | 1.23 V _{RHE} | 0.5 M H ₂ SO ₄ | 230 |
| NiO@g-CN | 0.00865 | 0.7 V _{SCE} | 0.5 M Na ₂ SO ₄ | 231 |
| BWO QDs/CN | 0.00039 | 1.23 V _{RHE} | 0.2 M Na ₂ SO ₄ | 232 |
| SCN/BWO | 0.0574 | 1.23 V _{RHE} | 1 M KOH | 233 |
| CZO | 0.162 | V _{Ag/AgCl} | 0.1 M Na ₂ SO ₃ | 235 |
| g-C ₃ N ₄ -BiVO ₄ | 0.00202 | 1.23 V _{RHE} | 1 M KOH | 236 |
| BiVO ₄ /g-C ₃ N ₄ | 1.14 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ buffered with a 1 M Na ₂ SO ₃ | 237 |
| BV/CN-5 | 0.7 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 239 |
| BiVO ₄ /g-C ₃ N ₄ -NS | 3.12 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ | 240 |
| g-C ₃ N ₄ /Mo:BiVO ₄ | 3.11 | 1.23 V _{RHE} | 0.1 M KH ₂ PO ₄ | 241 |
| NiFeO _x /B-C ₃ N ₄ /Mo:BiVO ₄ | 5.93 | 1.23 V _{RHE} | PPB | 242 |
| γ-g-C ₃ N ₄ @BiVO ₄ | 1.38 | V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 243 |
| g-C ₃ N ₄ /BiVO ₄ (30%) | 0.00046 | V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 244 |
| BiVO ₄ /g-CN | 7.4 | 2.2 V _{RHE} | 0.1 M KH ₂ PO ₄ + 1 M Na ₂ SO ₃ | 245 |
| C ₃ N ₄ /InVO ₄ | 0.013 | 0.9 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 246 |
| FeVO ₄ /C ₃ N ₄ | 0.18 | 0.7 V _{SCE} | 0.1 M Na ₂ SO ₄ | 247 |
| mt-CN/MoS ₂ | 0.16 | 0.5 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 251 |
| MoS ₂ /g-C ₃ N ₄ | 0.07 | -0.8 V _{Ag/AgCl} | 0.1 M H ₂ SO ₄ | 252 |
| g-C ₃ N ₄ /Bi ₂ S ₃ /BiNPs | 7.11 | 1.23 V _{RHE} | 0.1 M Na ₂ SO ₄ + 0.1 M Na ₂ SO ₃ | 253 |
| CNIS25 | 0.0078 | 1.5 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₃ | 254 |
| In ₂ S ₃ /S-C ₃ N ₄ -dots-20 | 4.93 | 1.18 V _{RHE} | 3.5 wt% NaCl solution and Na ₂ SO ₄ | 255 |
| g-C ₃ N ₄ /CdS | 5.4 | 0.2 V _{Ag/AgCl} | 0.5 M Na ₂ S + 0.5 M Na ₂ SO ₃ | 256 |
| Ag@g-C ₃ N ₄ /ZnS | 0.2 | 1.60 V _{RHE} | 1 M KOH | 257 |
| DPCN/NRGO/NiFe-LDH | 0.1623 | 1.4 V _{RHE} | 0.01 M Na ₂ SO ₄ | 261 |
| CoMn-LDH/g-C ₃ N ₄ | 0.227 | V _{Ag/AgCl} | 1 M KOH | 262 |
| CoFe-LDH@g-C ₃ N ₄ | 0.196 | V _{RHE} | 1 M KOH | 263 |
| CNN G3 LDH | 0.97 | 0.61 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 265 |
| CuTi-LDH/C ₃ N ₄ | 0.014 | V _{RHE} | 1 M KOH | 266 |
| C ₃ N ₄ @CuAF/Ni(OH) ₂ | 0.32 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 268 |
| 6%g-C ₃ N ₄ /BiOF | 0.0482 | 1.23 V _{RHE} | 0.5 M NaOH | 270 |
| 6%g-C ₃ N ₄ /BiOI | 0.1316 | V _{RHE} | 0.5 M Na ₂ SO ₃ + NaHCO ₃ | 271 |
| Nd:g-C ₃ N ₄ /BiOI | 1.55 | 1.23 V _{RHE} | 0.5 M Na ₂ SO ₄ | 273 |
| Bi ₂ MoO ₆ /g-C ₃ N ₄ | 0.520 | 0.7 V _{SCE} | 0.1 M Na ₂ SO ₄ | 274 |
| g-C ₃ N ₄ /Bi ₂ O ₃ /BiPO ₄ | 0.095 | 1.25 V _{Ag/AgCl} | 0.1 M Na ₂ SO ₄ | 275 |
| g-C ₃ N ₄ /ThO ₂ | 0.00971 | 1.23 V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 276 |
| CN/Mn ₂ O ₃ /FTO | 0.093 | 0.8 V _{RHE} | 0.1 M Na ₂ SO ₄ | 277 |
| AgNi/g-C ₃ N ₄ | 1.29 | 1 V _{Ag/AgCl} | 1.0 M NaOH | 278 |
| SiNWS/g-C ₃ N ₄ | 0.045 | 0 V _{Pt} | 0.5 M Na ₂ SO ₄ | 279 |
| g-C ₃ N ₄ /SiC | 0.015 | V _{SCE} | 0.5 M Na ₂ SO ₄ | 280 |
| CoP-CN | 0.15 | 0.4 V _{Ag/AgCl} | 0.5 M Na ₂ SO ₄ | 282 |
| CoOx/C ₃ N ₄ /Ba-TaON | 4.57 | 1.23 V _{RHE} | 1 M NaOH | 285 |

films on a polycrystalline CuInS₂ chalcopyrite substrate.²⁹² The electrode showed good activity and stability with g-C₃N₄ acting

as a protective layer for semiconducting CuInS₂, inhibiting degradation and photo-corrosion under acidic conditions.



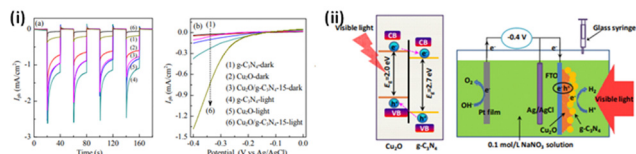


Fig. 8 (i) (a) Transient photocurrent response at a bias potential of -0.4 V (vs. Ag/AgCl) under visible light: [(1) Cu_2O ; (2) $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4-5$; (3) $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4-10$; (4) $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4-15$; (5) $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4-20$; (6) $\text{g-C}_3\text{N}_4$]. (b) Linear sweep voltammograms of Cu_2O , $\text{g-C}_3\text{N}_4$ and $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4-15$ films in the dark and under visible light. (ii) Schematic pathway for photoelectron transfer and the photoelectrochemical process in $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4$ film under visible light irradiation. Reprinted from ref. 151 with permission.

While the solar spectral range up to 460 nm was captured by the high band gap $\text{g-C}_3\text{N}_4$ material, the red portion was absorbed by the low band gap CuInS_2 (~ 1.5 eV) semiconducting electrode with a smaller band gap. The generation of cathodic photocurrents with an onset potential of $+0.21$ V_{RHE} in 0.1 M H_2SO_4 aqueous solution was observed over polycrystalline CuInS_2 , and the introduction of C_3N_4 enhanced the onset potential to 0.36 V_{RHE} . The design and development of a $\text{C}_3\text{N}_4-x\text{S}_{3x/2}/\text{CdS}/\text{CuIn}_{0.7}\text{Ga}_{0.3}\text{S}_2$ photocathode with optimally aligned energy levels to facilitate photoactivity was undertaken by Wang *et al.*²⁹³ The alteration of the CdS/CIGS materials using a stable and band-aligned protecting layer of S-doped C_3N_4 could satisfy the requisites for highly efficient water reduction materials. A molten-salt-based synthetic approach was adopted for the preparation of Cu-modified $\text{g-C}_3\text{N}_4$ with superior photocathodic performance on account of the coordination effect of Cu and the formation of a type II heterojunction due to *in situ* generation of CuCl .²⁹⁴ After the photoexcitation to the CB of coordinated C_3N_4 and then to the CB of CuCl , the electrons were expended for H_2 generation.

Biopolymer-activation of g-CN *via* soft-templating and the incorporation of active carbon-dopant sites was demonstrated

by Zhang *et al.*²⁹⁵ Two biopolymers, alginate and gelatin, were used as activating agents for $\text{g-C}_3\text{N}_4$. Synergistic interactions between the $\text{g-C}_3\text{N}_4$ precursor and biopolymer precursor induced a sponge-like porosity and simultaneous C doping, leading to enhanced PEC activity. Carbon doping enhances the conjugation, thereby extending the absorption edge. Electric-field-assisted charge transfer at the interfaces has been utilised to construct ZnO nanotube array-decorated $\text{g-C}_3\text{N}_4$ particles with improved photocathodic performance.²⁹⁶ Grafting of CoSe_2 nanorods into $\text{g-C}_3\text{N}_4$ nanosheets reduced the charge accumulation on CoSe_2 , providing greater stability. Basu *et al.* reported $\text{g-C}_3\text{N}_4-\text{CoSe}_2$ decorated on p-Si MWs that could function as stable and competent photocathodes for PEC H_2 evolution.¹²⁰ The efficient snatching of photogenerated electrons by CoSe_2 and the subsequent transfer to the Si surface and the electrolyte explained the high performance. The as-prepared p-Si/ $\text{C}_3\text{N}_4-\text{CoSe}_2$ heterostructure could afford a photocurrent density of -4.89 mA cm^{-2} at 0 V_{RHE} . Owing to the more positive valence band potential of $\text{g-C}_3\text{N}_4$ relative to NiO, it can act as a cocatalyst and photosensitizer for the NiO photocathode, capable of injecting holes into p-type NiO.²⁹⁷ The photocathodes exhibited excellent stability in both air and N_2 -saturated neutral environments. A 0D/2D $\text{AgVO}_3/\text{g-C}_3\text{N}_4$ photocathode exhibited a high photocurrent density of -1.02 mA cm^{-2} at 0 V_{RHE} .²⁹⁸ Enhancing the efficiency of the $\text{g-C}_3\text{N}_4$ photocathode *via* the o-catalyst decoration technique was attempted by Shanker *et al.*²⁹⁹ An extended interface for the efficient separation of photoexcited electron-hole pairs through electron transfer from $\text{g-C}_3\text{N}_4$ to N graphene-titanium nitride (TiN-NFG) could be achieved in $\text{C}_3\text{N}_4:\text{TiN-NFG}$ nanocrystals. A stable 2D/2D heterojunction $\text{g-C}_3\text{N}_4/\text{graphydine}$ was prepared by simple $\pi-\pi$ stacking interactions. The incorporation of Pt nanoparticles on $\text{g-C}_3\text{N}_4$ increased the photocurrent.³⁰⁰ Gopalakrishnan *et al.* reported silicon nanowire-based hybrid nanostructures comprised of SrTiO_3 nanoparticle-coupled $\text{g-C}_3\text{N}_4$ nanosheets as photocathodes. The hybrid heterojunction

Table 2 PEC performance of $\text{g-C}_3\text{N}_4$ -based photocathodes

| System | Photocurrent density (mA cm^{-2}) | Potential | Electrolyte | Ref. |
|--|--|------------------------------------|---|------|
| ZnO/Au/ $\text{g-C}_3\text{N}_4$ | -0.29 | 0 V_{RHE} | 0.2 M Na_2SO_4 | 99 |
| $\text{g-C}_3\text{N}_4/\text{CuO}$ | -0.85 | 0 V_{RHE} | 0.1 M Na_2SO_4 | 118 |
| Si/ $\text{C}_3\text{N}_4-\text{CoSe}_2-100$ | -8.4 | -0.289 V_{RHE} | 0.5 M H_2SO_4 | 120 |
| $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4$ | -1.38 | -0.4 $V_{\text{Ag}/\text{AgCl}}$ | 0.1 M NaNO_3 | 124 |
| $\text{Cu}_2\text{O}/\text{g-C}_3\text{N}_4/\text{WS}_2$ | -9.5 | -0.55 V_{RHE} | 1 M Na_2SO_4 | 286 |
| Cu_2O foam/ $\text{g-C}_3\text{N}_4$ | -2.5 | 0 V_{RHE} | 0.1 M Na_2SO_4 | 287 |
| C-CuO/CN | -2.85 | 0 V_{RHE} | 0.1 M Na_2SO_4 | 288 |
| $\text{g-C}_3\text{N}_4/\text{CuInS}_2$ | -0.3 | -0.6 $V_{\text{Ag}/\text{AgCl}}$ | 0.1 M H_2SO_4 | 292 |
| $\text{C}_3\text{N}_4-x\text{S}_{3x/2}/\text{CdS}/\text{CIGS}$ | -5 | -0.3 V_{RHE} | 1 M $\text{K}_2\text{HPO}_4/\text{KH}_2\text{PO}_4$ | 293 |
| Cu-CN-W | -0.200 | 0.42 V_{RHE} | 0.2 M Na_2SO_4 | 294 |
| $\text{g-C}_3\text{N}_4/\text{NiO}/\text{FTO}$ | -0.02 | 0 V_{RHE} | 0.1 M Na_2SO_4 | 297 |
| $\text{AgVO}_3/\text{g-C}_3\text{N}_4$ | -1.02 | 0 V_{RHE} | 1 M Na_2SO_4 | 298 |
| $\text{g-C}_3\text{N}_4:\text{TiN-NFG}$ | -0.196 | 0.11 V_{RHE} | 0.5 M Na_2SO_4 and 10 vol% TEOA | 299 |
| Pt@ $\text{g-C}_3\text{N}_4/\text{GDY}$ | -0.133 | 0 V_{RHE} | 0.1 M Na_2SO_4 | 300 |
| Hybrid Si NWs@ $\text{g-C}_3\text{N}_4$ NSS-SrTiO ₃ NPs | -28 | 1.23 V_{RHE} | 0.5 M Na_2SO_4 | 301 |
| $\text{g-C}_3\text{N}_4:\text{ITO}$ | -0.070 | 1 V_{RHE} | 0.5 M Na_2SO_4 | 302 |
| CN/TO/PTO film | -0.0685 | 0 $V_{\text{Ag}/\text{AgCl}}$ | 0.1 M Na_2SO_4 | 304 |
| $\text{LaFeO}_3/\text{g-C}_3\text{N}_4$ | -0.004 | -0.3 $V_{\text{Ag}/\text{AgCl}}$ | 0.1 M Na_2SO_4 | 305 |
| ZnSe/ $\text{g-C}_3\text{N}_4$ | -0.5 | $V_{\text{Ag}/\text{AgCl}}$ | 0.5 M Na_2SO_4 | 306 |
| h-PCN | -0.1 | V_{RHE} | 0.5 M H_2SO_4 | 307 |



photocathode exhibited a photocurrent density of -28 mA cm^{-2} at neutral pH. The PEC water reduction activity was ascribed to the formation of a built-in potential electrode/electrolyte interface due to charge separation and migration from Si NWs to the interfacial heterojunction layer.²⁷⁶ With a bias of 0 V_{RHE} in a neutral electrolyte, the Z-scheme $\text{ZnO}/\text{Au}/\text{g-C}_3\text{N}_4$ photocathode exhibited a stable photocurrent of -0.29 mA cm^{-2} in the presence of a Pt co-catalyst. On account of its high work function (-5.30 eV), Au NPs mediated the electron transfer from ZnO to $\text{g-C}_3\text{N}_4$, completing a direct Z-scheme charge-carrier process.³⁰¹ Shanker *et al.* introduced Sn-doped In_2O_3 (ITO) nanocrystals as co-catalysts for $\text{g-C}_3\text{N}_4$, generating a six-fold activity enhancement.³⁰² A type-II ferroelectric-semiconductor heterojunction of $\text{g-C}_3\text{N}_4$ with BiFeO_3 has been reported.³⁰³ Another ferroelectric material, PbTiO_3 (PTO) when combined with $\text{g-C}_3\text{N}_4$ formed Z-scheme heterojunctions with TiO_2 inserted between PTO and $\text{g-C}_3\text{N}_4$ to form a buffer layer.³⁰⁴ The deposition of LaFeO_3 at the surface of the $\text{g-C}_3\text{N}_4$ film *via* magnetron sputtering followed by oxidation was reported by Gries *et al.*³⁰⁵ A type-II heterostructure $\text{ZnSe}/\text{g-C}_3\text{N}_4$ obtained by implanting the ZnSe nanoflowers into the $\text{g-C}_3\text{N}_4$ framework aided by ultrasonication was tested for PEC water splitting.³⁰⁶ The photocurrent enhancement for $\text{g-C}_3\text{N}_4$ in the cathodic direction could be achieved by P doping employing trioctylphosphine oxide as a dopant precursor.³⁰⁷ Table 2 provides the PEC performance of $\text{g-C}_3\text{N}_4$ -based photocathodes.

4. Conclusion and perspectives

This review delivers a comprehensive depiction of $\text{g-C}_3\text{N}_4$ -based materials for PEC water splitting. Considering the requirements for the VB and CB positions, $\text{g-C}_3\text{N}_4$ can be used both as a photocathode and anode. Nonetheless, its inherent shortcomings such as small surface area, low electrical conductivity and rapid electron–hole recombination limit its PEC activity. In general, the low photocurrent density exhibited by pristine $\text{g-C}_3\text{N}_4$ impairs its potential to meet commercial demands. High-quality $\text{g-C}_3\text{N}_4$ films are essential for efficient light absorption and charge generation in the PEC water splitting procedure. To achieve maximal activity, the $\text{g-C}_3\text{N}_4$ films should be homogeneous, continuous, and in good contact with the substrate. For the synthesis of $\text{g-C}_3\text{N}_4$ films, innovative bottom-up methodologies should be used since they mitigate the poor dispersibility and solubility problems of $\text{g-C}_3\text{N}_4$, which are often present in top-down approaches for $\text{g-C}_3\text{N}_4$ film fabrication.

New hybrid non-vacuum-based synthetic protocols to obtain homogeneous and crack-free films with good adhesion to the conductive substrate should be developed with controllable thickness to fabricate the large surface area thin film photoelectrodes. The process of the synthesis of films should modulate and control the intrinsic π -conjugated structure for $\text{g-C}_3\text{N}_4$ light absorption and conversion to be further increased, resulting from substantial alterations to its electronic state, band structure, and optical/electrical characteristics. A few

strategies that can be investigated to modulate the intrinsic properties to achieve ideal PEC performance include heteroatom doping, defect engineering, and the introduction of functional groups into the $\text{g-C}_3\text{N}_4$ matrix. The controllable changes in functional groups on the surface can improve the investigations and control over the surface plane fabrication, adhesion and charge transfer. Morphological nano levels can also aid in improving the PEC performance. There is ample scope for exploring the impact of various hierarchical nanostructures, including nanoparticles, nanorods, *etc.*, on PEC performance.

The decoration of hole-transporting layers (HTLs) and ETLs (electron-transporting layers) with minimum to no parasitic light absorption should be studied. The stable intermediate layers to avoid the direct contact of electrolyte and light absorbing layer should be of utmost priority for the longevity of the electrode. The investigation of effective oxidation/reduction cocatalysts that align well with the charge capturing from the bulk layers of $\text{g-C}_3\text{N}_4$ is essential since the activation energy of water oxidation is the limiting step for overall water splitting. Photo-generated charge carriers can be effectively separated, and their recombination can be suppressed by the cocatalyst by providing specific active surface sites to participate in the reduction and oxidation reaction. To accomplish efficient charge transfer, good interfacial contact between the cocatalyst and $\text{g-C}_3\text{N}_4$ must be sustained using buffer layers. The cocatalyst introduction can also reduce the overpotential for the HER and OER. The formation of type-II or Z-scheme heterojunctions with other semiconductors can facilitate high charge mobility, thereby reducing the prospects of electron–hole recombination; the metal oxides, double oxides, and chalcogenides are widely explored in this category. Integration with conductive matrices like graphene improves electronic conductivity and provides channels for electron transfer. The plasmonic effect of the metal nanoparticles loading may be beneficial in widening the light absorption and increasing the charge carrier concentration. Long-term and large-scale applications of $\text{g-C}_3\text{N}_4$ -based photoelectrodes rely substantially on their stability and feasibility to manufacture large surface area films economically. Additional research on the modified technologies is necessary to ensure a steady run. This includes applying protective layers and achieving strong adherence of $\text{g-C}_3\text{N}_4$ films on substrates. Theoretical studies should be taken into consideration for understanding the charge transfer kinetics and mechanism assisting the rational design of systems for efficient PEC water splitting and relieving experimental workload and chemical cost. DFT studies are useful for comprehending the fundamental process of the improvement of PEC activity brought about by different modification techniques at the atomic or unit-cell scale. Clarifying the kinetics of charge transfer in a functional photoelectrode and gaining a thorough grasp of charge transfer and recombination in semiconductor materials is crucial. Consequently, it would be ideal to use *in situ* spectroscopic studies to observe charge transfer kinetics, phase changes, and reactive reaction intermediates in real time. Additional sophisticated spectroscopic



techniques, like time-resolved fluorescence measurements, transient absorption spectroscopy, and time-resolved microwave conductivity, could be useful in elucidating the relevant photoelectrochemical processes. The PEC application of $g\text{-C}_3\text{N}_4$ is still in the early phase. With the intensive perpetual research in the field, $g\text{-C}_3\text{N}_4$ may emerge as a potential durable system for PEC applications in the coming years.

Author contributions

Merin Joseph: conceptualization, data curation, writing – original draft, Mohit Kumar: writing – reviewing and editing, Suja Haridas: supervision, writing – reviewing and editing, Challapalli Subrahmanyam: supervision, writing – reviewing and editing, Sebastian Nybin Remello: supervision.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The financial support from SMNRI funding, UGC-SAP, DST-PURSE, DST-FIST and RUSA 2.0 grants are acknowledged. The fellowships from Cochin University of Science and Technology in Cochin, Kerala, and RUSA 2.0 are also acknowledged.

References

- C. V. Reddy, K. R. Reddy, N. P. Shetti, J. Shim, T. M. Aminabhavi and D. D. Dionysiou, *Int. J. Hydrogen Energy*, 2020, **45**, 18331–18347.
- C. Daulbayev, F. Sultanov, B. Bakbolat and O. Daulbayev, *Int. J. Hydrogen Energy*, 2020, **45**, 33325–33342.
- R. Gao, J. Zhu and D. Yan, Transition metal-based layered double hydroxides for photo (electro) chemical water splitting: a mini review, *Nanoscale*, 2021, **13**(32), 13593–13603.
- L. Bai, H. Huang, S. Yu, D. Zhang, H. Huang and Y. Zhang, Role of transition metal oxides in $g\text{-C}_3\text{N}_4$ -based heterojunctions for photocatalysis and supercapacitors, *J. Energy Chem.*, 2022, **64**, 214–235.
- Y. Wang, L. Liu, T. Ma, Y. Zhang and H. Huang, 2D graphitic carbon nitride for energy conversion and storage, *Adv. Funct. Mater.*, 2021, **31**(34), 2102540.
- W. Yang, R. R. Prabhakar, J. Tan, S. D. Tilley and J. Moon, Strategies for enhancing the photocurrent, photovoltage, and stability of photoelectrodes for photoelectrochemical water splitting, *Chem. Soc. Rev.*, 2019, **48**(19), 4979–5015.
- M. A. Desai, A. N. Vyas, G. D. Saratale and S. D. Sartale, Zinc oxide superstructures: recent synthesis approaches and application for hydrogen production via photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2019, **44**(4), 2091–2127.
- M. Ali, E. Pervaiz, U. Sikandar and Y. Khan, A review on the recent developments in zirconium and carbon-based catalysts for photoelectrochemical water-splitting, *Int. J. Hydrogen Energy*, 2021, **46**(35), 18257–18283.
- T. Higashi, H. Nishiyama, Y. Suzuki, Y. Sasaki, T. Hisatomi, M. Katayama, T. Minegishi, K. Seki, T. Yamada and K. Domen, Transparent Ta₃N₅ photoanodes for efficient oxygen evolution toward the development of tandem cells, *Angew. Chem., Int. Ed.*, 2019, **58**(8), 2300–2304.
- M. A. Mushtaq, A. Kumar, G. Yasin, M. Arif, M. Tabish, S. Ibraheem and X. Cai, *et al.*, 3D interconnected porous Mo-doped WO₃@ CdS hierarchical hollow heterostructures for efficient photoelectrochemical nitrogen reduction to ammonia, *Appl. Catal., B*, 2022, **317**, 121711.
- L. Pengyan, T. Zhang, M. A. Mushtaq, S. Wu, X. Xiang and D. Yan, Research progress in organic synthesis by means of photoelectrocatalysis, *Chem. Rec.*, 2021, **21**(4), 841–857.
- A. Fujishima and K. Honda, Electrochemical photolysis of water at a semiconductor electrode, *Nature*, 1972, **238**(5358), 37–38.
- A. G. Tamirat, J. Rick, A. A. Dubale, W.-N. Su and B.-J. Hwang, Using hematite for photoelectrochemical water splitting: a review of current progress and challenges, *Nanoscale Horiz.*, 2016, **1**(4), 243–267.
- P. Peerakiathajohn, J.-H. Yun, S. Wang and L. Wang, Review of recent progress in unassisted photoelectrochemical water splitting: from material modification to configuration design, *J. Photonics Energy*, 2017, **7**(1), 012006.
- P. Subrahmanyam, T. Vinodkumar, D. Nepak, M. Deepa and C. Subrahmanyam, Mo-doped BiVO₄@ reduced graphene oxide composite as an efficient photoanode for photoelectrochemical water splitting, *Catal. Today*, 2019, **325**, 73–80.
- K. Mika, K. Syrek, T. Uchacz, G. D. Sulka and L. Zaraska, Dark nanostructured ZnO films formed by anodic oxidation as photoanodes in photoelectrochemical water splitting, *Electrochim. Acta*, 2022, **414**, 140176.
- R.-B. Wei, P.-Y. Kuang, H. Cheng, Y.-B. Chen, J.-Y. Long, M.-Y. Zhang and Z.-Q. Liu, Plasmon-enhanced photoelectrochemical water splitting on gold nanoparticle decorated ZnO/CdS nanotube arrays, *ACS Sustainable Chem. Eng.*, 2017, **5**(5), 4249–4257.
- P. Kumar, P. Sharma, R. Shrivastav, S. Dass and V. R. Satsangi, Electrodeposited zirconium-doped $\alpha\text{-Fe}_2\text{O}_3$ thin film for photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2011, **36**(4), 2777–2784.
- G. Wang, H. Wang, Y. Ling, Y. Tang, X. Yang, R. C. Fitzmorris, C. Wang, J. Z. Zhang and Y. Li, Hydrogen-treated TiO₂ nanowire arrays for photoelectrochemical water splitting, *Nano Lett.*, 2011, **11**(7), 3026–3033.
- V. Cristino, S. Caramori, R. Argazzi, L. Meda, G. L. Marra and C. A. Bignozzi, Efficient photoelectrochemical water splitting by anodically grown WO₃ electrodes, *Langmuir*, 2011, **27**(11), 7276–7284.
- Z. Liu, X. Lu and D. Chen, Photoelectrochemical water splitting of CuInS₂ photocathode collaborative modified with separated catalysts based on efficient photogenerated electron-hole separation, *ACS Sustainable Chem. Eng.*, 2018, **6**(8), 10289–10294.



- 22 D. Sharma, S. Upadhyay, V. R. Satsangi, R. Shrivastav, U. V. Waghmare and S. Dass, Improved photoelectrochemical water splitting performance of $\text{Cu}_2\text{O}/\text{SrTiO}_3$ heterojunction photoelectrode, *J. Phys. Chem. C*, 2014, **118**(44), 25320–25329.
- 23 S. Bai, J. Han, K. Zhang, Y. Zhao, R. Luo, D. Li and A. Chen, rGO decorated semiconductor heterojunction of BiVO_4/NiO to enhance PEC water splitting efficiency, *Int. J. Hydrogen Energy*, 2022, **47**(7), 4375–4385.
- 24 H. She, M. Jiang, P. Yue, J. Huang, L. Wang, J. Li, G. Zhu and Q. Wang, Metal ($\text{Ni}^{2+}/\text{Co}^{2+}$) sulfides modified BiVO_4 for effective improvement in photoelectrochemical water splitting, *J. Colloid Interface Sci.*, 2019, **549**, 80–88.
- 25 S. Chandrasekaran, L. Yao, L. Deng, C. Bowen, Y. Zhang, S. Chen, Z. Lin, F. Peng and P. Zhang, Recent advances in metal sulfides: from controlled fabrication to electrocatalytic, photocatalytic and photoelectrochemical water splitting and beyond, *Chem. Soc. Rev.*, 2019, **48**(15), 4178–4280.
- 26 N. Han, P. Liu, J. Jiang, L. Ai, Z. Shao and S. Liu, Recent advances in nanostructured metal nitrides for water splitting, *J. Mater. Chem. A*, 2018, **6**(41), 19912–19933.
- 27 M. Wu, Q. Wang, Q. Sun and P. Jena, Functionalized graphitic carbon nitride for efficient energy storage, *J. Phys. Chem. C*, 2013, **117**(12), 6055–6059.
- 28 Y. Luo, Y. Yan, S. Zheng, H. Xue and H. Pang, Graphitic carbon nitride based materials for electrochemical energy storage, *J. Mater. Chem. A*, 2019, **7**(3), 901–924.
- 29 A. Thomas, A. Fischer, F. Goettmann, M. Antonietti, J.-O. Müller, R. Schlögl and J. M. Carlsson, Graphitic carbon nitride materials: variation of structure and morphology and their use as metal-free catalysts, *J. Mater. Chem.*, 2008, **18**(41), 4893–4908.
- 30 X. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, A metal-free polymeric photocatalyst for hydrogen production from water under visible light, *Nat. Mater.*, 2009, **8**(1), 76–80.
- 31 Y. Zhang, J. Liu, G. Wu and W. Chen, Porous graphitic carbon nitride synthesized via direct polymerization of urea for efficient sunlight-driven photocatalytic hydrogen production, *Nanoscale*, 2012, **4**(17), 5300–5303.
- 32 G. Liu, G. Zhao, W. Zhou, Y. Liu, H. Pang, H. Zhang and D. Hao, *et al.*, In situ bond modulation of graphitic carbon nitride to construct p–n homojunctions for enhanced photocatalytic hydrogen production, *Adv. Funct. Mater.*, 2016, **26**(37), 6822–6829.
- 33 Q. Liang, Z. Li, Z.-H. Huang, F. Kang and Q.-H. Yang, Holey graphitic carbon nitride nanosheets with carbon vacancies for highly improved photocatalytic hydrogen production, *Adv. Funct. Mater.*, 2015, **25**(44), 6885–6892.
- 34 M. Wei, L. Gao, J. Li, J. Fang, W. Cai, X. Li and A. Xu, Activation of peroxydisulfate by graphitic carbon nitride loaded on activated carbon for organic pollutants degradation, *J. Hazard. Mater.*, 2016, **316**, 60–68.
- 35 D. Rattan Paul and S. P. Nehra, Graphitic carbon nitride: a sustainable photocatalyst for organic pollutant degradation and antibacterial applications, *Environ. Sci. Pollut. Res.*, 2021, **28**, 3888–3896.
- 36 J. Mao, T. Peng, X. Zhang, K. Li, L. Ye and L. Zan, Effect of graphitic carbon nitride microstructures on the activity and selectivity of photocatalytic CO_2 reduction under visible light, *Catal. Sci. Technol.*, 2013, **3**(5), 1253–1260.
- 37 P. Xia, B. Zhu, J. Yu, S. Cao and M. Jaroniec, Ultra-thin nanosheet assemblies of graphitic carbon nitride for enhanced photocatalytic CO_2 reduction, *J. Mater. Chem. A*, 2017, **5**(7), 3230–3238.
- 38 Y. Zhang and M. Antonietti, Photocurrent generation by polymeric carbon nitride solids: an initial step towards a novel photovoltaic system, *Chem. – Asian J.*, 2010, **5**(6), 1307–1311.
- 39 L. Wang, Y. Tong, J. Feng, J. Hou, J. Li, X. Hou and J. Liang, $\text{g-C}_3\text{N}_4$ -based films: A rising star for photoelectrochemical water splitting, *Sustainable Mater. Technol.*, 2019, **19**, e00089.
- 40 X. Zou, Z. Sun and Y. H. Hu, $\text{g-C}_3\text{N}_4$ -based photoelectrodes for photoelectrochemical water splitting: A review, *J. Mater. Chem. A*, 2020, **8**(41), 21474–21502.
- 41 L. Wang, W. Si, Y. Tong, F. Hou, D. Pergolesi, J. Hou, T. Lippert, S. X. Dou and J. Liang, Graphitic carbon nitride ($\text{g-C}_3\text{N}_4$)-based nanosized heteroarrays: promising materials for photoelectrochemical water splitting, *Carbon Energy*, 2020, **2**(2), 223–250.
- 42 R. Koutavarapu, S. G. Peera, T. G. Lee, C. R. Myla, D.-Y. Lee, J. Shim and S. K. Balasingam, Recent trends in graphitic carbon nitride-based binary and ternary heterostructured electrodes for photoelectrochemical water splitting, *Processes*, 2021, **9**(11), 1959.
- 43 J. Safaei, N. A. Mohamed, M. F. M. Noh, M. F. Soh, N. A. Ludin, M. A. Ibrahim, W. N. R. W. Isahak and M. A. M. Teridi, Graphitic carbon nitride ($\text{g-C}_3\text{N}_4$) electrodes for energy conversion and storage: a review on photoelectrochemical water splitting, solar cells and supercapacitors, *J. Mater. Chem. A*, 2018, **6**(45), 22346–22380.
- 44 W. Xiong, F. Huang and R.-Q. Zhang, Recent developments in carbon nitride based films for photoelectrochemical water splitting, *Sustainable Energy Fuels*, 2020, **4**(2), 485–503.
- 45 M. Volokh, G. Peng, J. Barrio and M. Shalom, Carbon nitride materials for water splitting photoelectrochemical cells, *Angew. Chem., Int. Ed.*, 2019, **58**(19), 6138–6151.
- 46 N. Z. Muradov and T. N. Veziroğlu, “Green” path from fossil-based to hydrogen economy: an overview of carbon-neutral technologies, *Int. J. Hydrogen Energy*, 2008, **33**(23), 6804–6839.
- 47 S. S. Penner, Steps toward the hydrogen economy, *Energy*, 2006, **31**(1), 33–43.
- 48 G. Marbán and T. Valdés-Solís, Towards the hydrogen economy?, *Int. J. Hydrogen Energy*, 2007, **32**(12), 1625–1637.
- 49 T. Grewe, M. Meggouh and H. Tüesues, Nanocatalysts for solar water splitting and a perspective on hydrogen economy, *Chem. – Asian J.*, 2016, **11**(1), 22–42.
- 50 W. C. Nadaleti, E. G. de Souza and S. N. M. de Souza, The potential of hydrogen production from high and low-temperature electrolysis methods using solar and nuclear energy sources: The transition to a hydrogen economy in Brazil, *Int. J. Hydrogen Energy*, 2022, **47**(82), 34727–34738.



- 51 M.-K. Kazi, F. Eljack, M. M. El-Halwagi and M. Haouari, Green hydrogen for industrial sector decarbonization: Costs and impacts on hydrogen economy in qatar, *Comput. Chem. Eng.*, 2021, **145**, 107144.
- 52 J. Joy, J. Mathew and S. C. George, Nanomaterials for photoelectrochemical water splitting—review, *Int. J. Hydrogen Energy*, 2018, **43**(10), 4804–4817.
- 53 M. A. Marwat, M. Humayun, M. W. Afridi, H. Zhang, M. R. Abdul Karim, M. Ashtar and M. Usman, *et al.*, Advanced catalysts for photoelectrochemical water splitting, *ACS Appl. Energy Mater.*, 2021, **4**(11), 12007–12031.
- 54 M. Joseph and S. Haridas, Recent progresses in porphyrin assisted hydrogen evolution, *Int. J. Hydrogen Energy*, 2020, **45**(21), 11954–11975.
- 55 P. Subramanyam, B. Meena, V. Biju, H. Misawa and S. Challapalli, Emerging materials for plasmon-assisted photoelectrochemical water splitting, *J. Photochem. Photobiol., C*, 2022, **51**, 100472.
- 56 Y.-H. Chiu, T.-H. Lai, M.-Y. Kuo, P.-Y. Hsieh and Y.-J. Hsu, Photoelectrochemical cells for solar hydrogen production: Challenges and opportunities, *APL Mater.*, 2019, **7**(8), 1–11.
- 57 H. Song, S. Luo, H. Huang, B. Deng and J. Ye, Solar-driven hydrogen production: Recent advances, challenges, and future perspectives, *ACS Energy Lett.*, 2022, **7**(3), 1043–1065.
- 58 Y. Asakura, T. Higashi, H. Nishiyama, H. Kobayashi, M. Nakabayashi, N. Shibata and T. Minegishi, *et al.*, Activation of a particulate Ta₃N₅ water-oxidation photoanode with a GaN hole-blocking layer, *Sustainable Energy Fuels*, 2018, **2**(1), 73–78.
- 59 S. Akiyama, M. Nakabayashi, N. Shibata, T. Minegishi, Y. Asakura, M. Abdulla-Al-Mamun and T. Hisatomi, *et al.*, Highly efficient water oxidation photoanode made of surface modified LaTiO₂N particles, *Small*, 2016, **12**(39), 5468–5476.
- 60 W.-T. Qiu, Y.-C. Huang, Z.-L. Wang, S. Xiao, H.-B. Ji and Y.-X. Tong, Effective strategies towards high-performance photoanodes for photoelectrochemical water splitting, *Acta Phys.-Chim. Sin.*, 2017, **33**(1), 80–102.
- 61 E. A. Kraut, R. W. Grant, J. R. Waldrop and S. P. Kowalczyk, Precise determination of the valence-band edge in x-ray photoemission spectra: application to measurement of semiconductor interface potentials, *Phys. Rev. Lett.*, 1980, **44**(24), 1620.
- 62 Q. Jia, K. Iwashina and A. Kudo, Facile fabrication of an efficient BiVO₄ thin film electrode for water splitting under visible light irradiation, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**(29), 11564–11569.
- 63 G. Hodes, D. Cahen and J. Manassen, Tungsten trioxide as a photoanode for a photoelectrochemical cell (PEC), *Nature*, 1976, **260**(5549), 312–313.
- 64 J. A. Seabold, K. Zhu and N. R. Neale, Efficient solar photoelectrolysis by nanoporous Mo: BiVO₄ through controlled electron transport, *Phys. Chem. Chem. Phys.*, 2014, **16**(3), 1121–1131.
- 65 S. Hoang, S. P. Berglund, N. T. Hahn, A. J. Bard and C. Buddie Mullins, Enhancing visible light photo-oxidation of water with TiO₂ nanowire arrays via cotreatment with H₂ and NH₃: synergistic effects between Ti³⁺ and N, *J. Am. Chem. Soc.*, 2012, **134**(8), 3659–3662.
- 66 T. Hisatomi and F. Le, Formal, M. Cornuz, J. Brillet, N. Tétreault, K. Sivula, and M. Grätzel, Cathodic shift in onset potential of solar oxygen evolution on hematite by 13-group oxide overlayers, *Energy Environ. Sci.*, 2011, **4**(7), 2512–2515.
- 67 A. J. Bard, Photoelectrochemistry and heterogeneous photo-catalysis at semiconductors, *J. Photochem.*, 1979, **10**(1), 59–75.
- 68 A. Thakur, D. Ghosh, P. Devi, K.-H. Kim and P. Kumar, Current progress and challenges in photoelectrode materials for the production of hydrogen, *Chem. Eng. J.*, 2020, **397**, 125415.
- 69 Q. Chen, G. Fan, H. Fu, Z. Li and Z. Zou, Tandem photoelectrochemical cells for solar water splitting, *Adv. Phys.: X*, 2018, **3**(1), 1487267.
- 70 O. Khaselev and J. A. Turner, A monolithic photovoltaic-photoelectrochemical device for hydrogen production via water splitting, *Science*, 1998, **280**(5362), 425–427.
- 71 Y. Zheng, L. Lin, B. Wang and X. Wang, Graphitic carbon nitride polymers toward sustainable photoredox catalysis, *Angew. Chem., Int. Ed.*, 2015, **54**(44), 12868–12884.
- 72 M. Huang, Y.-L. Zhao, W. Xiong, S. V. Kershaw, Y. Yu, W. Li, T. Dudka and R.-Q. Zhang, Collaborative enhancement of photon harvesting and charge carrier dynamics in carbon nitride photoelectrode, *Appl. Catal., B*, 2018, **237**, 783–790.
- 73 J. Xu, S. Cao, T. Brenner, X. Yang, J. Yu, M. Antonietti and M. Shalom, Supramolecular chemistry in molten sulfur: preorganization effects leading to marked enhancement of carbon nitride photoelectrochemistry, *Adv. Funct. Mater.*, 2015, **25**(39), 6265–6271.
- 74 F. Qi, Y. Li, Y. Wang, Y. Wang, S. Liu and X. Zhao, Ag-Doped g-C₃N₄ film electrode: fabrication, characterization and photoelectrocatalysis property, *RSC Adv.*, 2016, **6**(84), 81378–81385.
- 75 W. Zhang, J. Albero, L. Xi, K. M. Lange, H. Garcia, X. Wang and M. Shalom, One-pot synthesis of nickel-modified carbon nitride layers toward efficient photoelectrochemical cells, *ACS Appl. Mater. Interfaces*, 2017, **9**(38), 32667–32677.
- 76 J. Jing, Z. Chen and C. Feng, Dramatically enhanced photoelectrochemical properties and transformed p/n type of g-C₃N₄ caused by K and I co-doping, *Electrochim. Acta*, 2019, **297**, 488–496.
- 77 X. She, L. Liu, H. Ji, Z. Mo, Y. Li, L. Huang, D. Du, H. Xu and H. Li, Template-free synthesis of 2D porous ultrathin nonmetal-doped g-C₃N₄ nanosheets with highly efficient photocatalytic H₂ evolution from water under visible light, *Appl. Catal., B*, 2016, **187**, 144–153.
- 78 Z. Wang, X. Hu, G. Zou, Z. Huang, Z. Tang, Q. Liu, G. Hu and D. Geng, Advances in constructing polymeric carbon-nitride-based nanocomposites and their applications in energy chemistry, *Sustainable Energy Fuels*, 2019, **3**(3), 611–655.



- 79 F. K. Kessler, Y. Zheng, D. Schwarz, C. Merschjann, W. Schnick, X. Wang and M. J. Bojdys, Functional carbon nitride materials—design strategies for electrochemical devices. *Nature Reviews, Materials*, 2017, **2**(6), 1–17.
- 80 Y. Li, M. Zhou, B. Cheng and Y. Shao, Recent advances in g-C₃N₄-based heterojunction photocatalysts, *J. Mater. Sci. Technol.*, 2020, **56**, 1–17.
- 81 C.-H. Wang, D.-D. Qin, D.-L. Shan, J. Gu, Y. Yan, J. Chen and Q.-H. Wang, *et al.*, Assembly of g-C₃N₄-based type II and Z-scheme heterojunction anodes with improved charge separation for photoelectrojunction water oxidation, *Phys. Chem. Chem. Phys.*, 2017, **19**(6), 4507–4515.
- 82 G. K. Mor, O. K. Varghese, M. Paulose, K. Shankar and C. A. Grimes, A review on highly ordered, vertically oriented TiO₂ nanotube arrays: Fabrication, material properties, and solar energy applications, *Sol. Energy Mater. Sol. Cells*, 2006, **90**(14), 2011–2075.
- 83 G. Wang, Y. Ling, H. Wang, L. Xihong and Y. Li, Chemically modified nanostructures for photoelectrochemical water splitting, *J. Photochem. Photobiol., C*, 2014, **19**, 35–51.
- 84 B. Babu, J. Shim and K. Yoo, Efficient solar-light-driven photoelectrochemical water oxidation of one-step in-situ synthesized Co-doped g-C₃N₄ nanolayers, *Ceram. Int.*, 2020, **46**(10), 16422–16430.
- 85 A. E. A. Aboubakr, W. M. A. El Roubay, M. D. Khan, A. A. Farghali and N. Revaprasadu, ZnCr-CO₃ LDH/ruptured tubular g-C₃N₄ composite with increased specific surface area for enhanced photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2020, **508**, 145100.
- 86 P. Han, W. Martens, E. R. Waclawik, S. Sarina and H. Zhu, Metal nanoparticle photocatalysts: synthesis, characterization, and application, *Part. Part. Syst. Charact.*, 2018, **35**(6), 1700489.
- 87 G. Liu, K. Du, J. Xu, G. Chen, M. Gu, C. Yang, K. Wang and H. Jakobsen, Plasmon-dominated photoelectrodes for solar water splitting, *J. Mater. Chem. A*, 2017, **5**(9), 4233–4253.
- 88 A. Eftekhari, V. J. Babu and S. Ramakrishna, Photoelectrode nanomaterials for photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2017, **42**(16), 11078–11109.
- 89 F. Dong, Z. Zhao, Y. Sun, Y. Zhang, S. Yan and Z. Wu, An advanced semimetal-organic Bi spheres-g-C₃N₄ nanohybrid with SPR-enhanced visible-light photocatalytic performance for NO purification, *Environ. Sci. Technol.*, 2015, **49**(20), 12432–12440.
- 90 X. Fang, Y. Tang, Y.-J. Ma, G. Xiao, P. Li and D. Yan, Ultralong-lived triplet excitons of room-temperature phosphorescent carbon dots located on g-C₃N₄ to boost photocatalysis, *Sci. China Mater.*, 2023, **66**(2), 664–671.
- 91 P. Li, Y. Lin, Z. Qi and D. Yan, Efficient photoelectrocatalytic CO₂ reduction to CH₃OH via porous g-C₃N₄ nanosheets modified with cobalt phthalocyanine in ionic liquids, *J. Mater. Chem. A*, 2023, **11**(39), 21078–21088.
- 92 M. Joseph, N. K. Mohammed Sadik, S. N. Remello, S. Haridas and S. De, Through Space Sigma Donation π Acceptor Assisted Photocatalytic Degradation of Ciprofloxacin on TCPP Supported g-C₃N₄, *ChemistrySelect*, 2023, **8**(7), e202203348.
- 93 S. Lou, Z. Zhou, Y. Shen, Z. Zhan, J. Wang, S. Liu and Y. Zhang, Comparison study of the photoelectrochemical activity of carbon nitride with different photoelectrode configurations, *ACS Appl. Mater. Interfaces*, 2016, **8**(34), 22287–22294.
- 94 W. M. A. El Roubay, A. E. A. Aboubakr, M. D. Khan, A. A. Farghali, P. Millet and N. Revaprasadu, Synthesis and characterization of Bi-doped g-C₃N₄ for photoelectrochemical water oxidation, *Sol. Energy*, 2020, **211**, 478–487.
- 95 Y. Du, R. Ma, L. Wang, J. Qian and Q. Wang, 2D/1D BiOI/g-C₃N₄ nanotubes heterostructure for photoelectrochemical overall water splitting, *Sci. Total Environ.*, 2022, **838**, 156166.
- 96 A. E. A. Bakr, W. M. A. El Roubay, M. D. Khan, A. A. Farghali, B. Xulu and N. Revaprasadu, Synthesis and characterization of Z-scheme α -Fe₂O₃ NTs/ruptured tubular g-C₃N₄ for enhanced photoelectrochemical water oxidation, *Sol. Energy*, 2019, **193**, 403–412.
- 97 T. Song, X. Zhang and P. Yang, Bifunctional Nitrogen-Doped Carbon Dots in g-C₃N₄/WO_x Heterojunction for Enhanced Photocatalytic Water-Splitting Performance, *Langmuir*, 2021, **37**(14), 4236–4247.
- 98 K. M. Alam, P. Kumar, P. Kar, U. K. Thakur, S. Zeng, K. Cui and K. Shankar, Enhanced charge separation in g-C₃N₄-BiOI heterostructures for visible light driven photoelectrochemical water splitting, *Nanoscale Adv.*, 2019, **1**(4), 1460–1471.
- 99 P. Wen, Y. Sun, H. Li, Z. Liang, H. Wu, J. Zhang, H. Zeng, S. M. Geyer and L. Jiang, A highly active three-dimensional Z-scheme ZnO/Au/g-C₃N₄ photocathode for efficient photoelectrochemical water splitting, *Appl. Catal., B*, 2020, **263**, 118180.
- 100 Y. Fang, Y. Xu, X. Li, Y. Ma and X. Wang, Coating polymeric carbon nitride photoanodes on conductive Y: ZnO nanorod arrays for overall water splitting, *Angew. Chem.*, 2018, **130**(31), 9897–9901.
- 101 J. Safaei, N. A. Mohamed, M. F. Mohamad Noh, M. F. Soh, M. A. Riza, N. S. Mohamed Mustakim, N. A. Ludin, M. A. Ibrahim, W. N. R. W. Isahak and M. A. Mat Teridi, Facile fabrication of graphitic carbon nitride, (g-C₃N₄) thin film, *J. Alloys Compd.*, 2018, **769**, 130–135.
- 102 K. Li, X. Zeng, S. Gao, L. Ma, Q. Wang, H. Xu, Z. Wang, B. Huang, Y. Dai and J. Lu, Ultrasonic-assisted pyrolyzation fabrication of reduced SnO_{2-x}/g-C₃N₄ heterojunctions: Enhance photoelectrochemical and photocatalytic activity under visible LED light irradiation, *Nano Res.*, 2016, **9**, 1969–1982.
- 103 K. Li, Z. Huang, X. Zeng, B. Huang, S. Gao and J. Lu, Synergetic effect of Ti³⁺ and oxygen doping on enhancing photoelectrochemical and photocatalytic properties of TiO₂/g-C₃N₄ heterojunctions, *ACS Appl. Mater. Interfaces*, 2017, **9**(13), 11577–11586.
- 104 Y. Liu, F. Y. Su, Y. X. Yu and W. D. Zhang, Nano g-C₃N₄ modified Ti-Fe₂O₃ vertically arrays for efficient photoelectrochemical generation of hydrogen under visible light, *Int. J. Hydrogen Energy*, 2016, **41**(18), 7270–7279.
- 105 J. Safaei, H. Ullah, N. A. Mohamed, M. F. Mohamad Noh, M. F. Soh, A. A. Tahir, N. A. Ludin, M. A. Ibrahim,



- W. N. R. W. Isahak and M. A. Mat Teridi, Enhanced photoelectrochemical performance of Z-scheme g-C₃N₄/BiVO₄ photocatalyst, *Appl. Catal., B*, 2018, **234**, 296–310.
- 106 F. Liang and Y. Zhu, Enhancement of mineralization ability for phenol via synergetic effect of photoelectrocatalysis of g-C₃N₄ film, *Appl. Catal., B*, 2016, **180**, 324–329.
- 107 L. Liu, M. Wang and C. Wang, In-situ synthesis of graphitic carbon nitride/iron oxide–copper composites and their application in the electrochemical detection of glucose, *Electrochim. Acta*, 2018, **265**, 275–283.
- 108 H. Miao, G. Zhang, X. Hu, J. Mu, T. Han, J. Fan, C. Zhu, L. Song, J. Bai and X. Hou, A novel strategy to prepare 2D g-C₃N₄ nanosheets and their photoelectrochemical properties, *J. Alloys Compd.*, 2017, **690**, 669–676.
- 109 J. Duan, S. Chen, M. Jaroniec and S. Z. Qiao, Porous C₃N₄ nanolayers@N-graphene films as catalyst electrodes for highly efficient hydrogen evolution, *ACS Nano*, 2015, **9**(1), 931–940.
- 110 X. Zhang, X. Xie, H. Wang, J. Zhang, B. Pan and Y. Xie, Enhanced photoresponsive ultrathin graphitic-phase C₃N₄ nanosheets for bioimaging, *J. Am. Chem. Soc.*, 2013, **135**(1), 18–21.
- 111 K. G. Zhou, D. McManus, E. Prestat, X. Zhong, Y. Shin, H. L. Zhang, S. J. Haigh and C. Casiraghi, Self-catalytic membrane photo-reactor made of carbon nitride nanosheets, *J. Mater. Chem. A*, 2016, **4**(30), 11666–11671.
- 112 E. J. Son, S. H. Lee, S. K. Kuk, M. Pesic, D. S. Choi, J. W. Ko, K. Kim, F. Hollmann and C. B. Park, Carbon Nanotube–Graphitic Carbon Nitride Hybrid Films for Flavoenzyme-Catalyzed Photoelectrochemical Cells, *Adv. Funct. Mater.*, 2018, **28**(24), 1705232.
- 113 Y. Wang, X. Zhao, Y. Tian, Y. Wang, A. K. Jan and Y. Chen, Facile Electrospinning Synthesis of Carbonized Polyvinylpyrrolidone (PVP)/g-C₃N₄ Hybrid Films for Photoelectrochemical Applications, *Chem. – Eur. J.*, 2017, **23**(2), 419–426.
- 114 Y. Wang, J. Sun, J. Li and X. Zhao, Electrospinning preparation of nanostructured g-C₃N₄/BiVO₄ composite films with an enhanced photoelectrochemical performance, *Langmuir*, 2017, **33**(19), 4694–4701.
- 115 C. He, J. H. Zhang, W. X. Zhang and T. T. Li, Type-II InSe/g-C₃N₄ heterostructure as a high-efficiency oxygen evolution reaction catalyst for photoelectrochemical water splitting, *J. Phys. Chem. Lett.*, 2019, **10**(11), 3122–3128.
- 116 G. Peng, M. Volokh, J. Tzadikov, J. Sun and M. Shalom, Carbon nitride/reduced graphene oxide film with enhanced electron diffusion length: an efficient photoelectrochemical cell for hydrogen generation, *Adv. Energy Mater.*, 2018, **8**(23), 1800566.
- 117 C. H. Choi, L. Lin, S. Gim, S. Lee, H. Kim, X. Wang and W. Choi, Polymeric carbon nitride with localized aluminum coordination sites as a durable and efficient photocatalyst for visible light utilization, *ACS Catal.*, 2018, **8**(5), 4241–4256.
- 118 H. Bae, V. Burungale, W. Na, H. Rho, S. H. Kang, S. W. Ryu and J. S. Ha, Nanostructured CuO with a thin g-C₃N₄ layer as a highly efficient photocathode for solar water splitting, *RSC Adv.*, 2021, **11**(26), 16083–16089.
- 119 J. Xu and M. Shalom, Electrophoretic deposition of carbon nitride layers for photoelectrochemical applications, *ACS Appl. Mater. Interfaces*, 2016, **8**(20), 13058–13063.
- 120 M. Basu, Z. W. Zhang, C. J. Chen, T. H. Lu, S. F. Hu and R. S. Liu, CoSe₂ embedded in C₃N₄: An efficient photocathode for photoelectrochemical water splitting, *ACS Appl. Mater. Interfaces*, 2016, **8**(40), 26690–26696.
- 121 S. Samanta, S. Martha and K. Parida, Facile synthesis of Au/g-C₃N₄ nanocomposites: an inorganic/organic hybrid plasmonic photocatalyst with enhanced hydrogen gas evolution under visible-light irradiation, *ChemCatChem*, 2014, **6**(5), 1453–1462.
- 122 C. Li, C. B. Cao and H. S. Zhu, Graphitic carbon nitride thin films deposited by electrodeposition, *Mater. Lett.*, 2004, **58**(12–13), 1903–1906.
- 123 D. Kang, T. W. Kim, S. R. Kubota, A. C. Cardiel, H. G. Cha and K. S. Choi, Electrochemical synthesis of photoelectrodes and catalysts for use in solar water splitting, *Chem. Rev.*, 2015, **115**(23), 12839–12887.
- 124 S. Zhang, J. Yan, S. Yang, Y. Xu, X. Cai, X. Li, X. Zhang, F. Peng and Y. Fang, Electrodeposition of Cu₂O/g-C₃N₄ heterojunction film on an FTO substrate for enhancing visible light photoelectrochemical water splitting, *Chin. J. Catal.*, 2017, **38**(2), 365–371.
- 125 H. Qi, B. Sun, J. Dong, L. Cui, T. Feng and S. Ai, Facile synthesis of two-dimensional tailored graphitic carbon nitride with enhanced photoelectrochemical properties through a three-step polycondensation method for photocatalysis and photoelectrochemical immunosensor, *Sens. Actuators, B*, 2019, **285**, 42–48.
- 126 D. B. Velusamy, M. A. Haque, M. R. Parida, F. Zhang, T. Wu, O. F. Mohammed and H. N. Alshareef, 2D organic–inorganic hybrid thin films for flexible UV–visible photodetectors, *Adv. Funct. Mater.*, 2017, **27**(15), 1605554.
- 127 L. Jia, H. Wang, D. Dhawale, C. Anand, M. A. Wahab, Q. Ji, K. Ariga and A. Vinu, Highly ordered macro-mesoporous carbon nitride film for selective detection of acidic/basic molecules, *Chem. Commun.*, 2014, **50**(45), 5976–5979.
- 128 H. Huang, R. Chen, J. Ma, L. Yan, Y. Zhao, Y. Wang, W. Zhang, J. Fan and X. Chen, Graphitic carbon nitride solid nanofilms for selective and recyclable sensing of Cu²⁺ and Ag⁺ in water and serum, *Chem. Commun.*, 2014, **50**(97), 15415–15418.
- 129 J. Bian, Q. Li, C. Huang, J. Li, Y. Guo, M. Zaw and R. Q. Zhang, Thermal vapor condensation of uniform graphitic carbon nitride films with remarkable photocurrent density for photoelectrochemical applications, *Nano Energy*, 2015, **15**, 353–361.
- 130 X. Lv, M. Cao, W. Shi, M. Wang and Y. Shen, A new strategy of preparing uniform graphitic carbon nitride films for photoelectrochemical application, *Carbon*, 2017, **117**, 343–350.
- 131 J. Bian, L. Xi, C. Huang, K. M. Lange, R.-Q. Zhang and M. Shalom, Efficiency enhancement of carbon nitride



- photoelectrochemical cells via tailored monomers design, *Adv. Energy Mater.*, 2016, **6**(12), 1600263.
- 132 J. Bian, L. Xi, J. Li, Z. Xiong, C. Huang, K. M. Lange, J. Tang, M. Shalom and R.-Q. Zhang, C=C π bond modified graphitic carbon nitride films for enhanced photoelectrochemical cell performance, *Chem. – Asian J.*, 2017, **12**(9), 1005–1012.
- 133 X. Lu, Z. Liu, J. Li, J. Zhang and Z. Guo, Novel framework g-C₃N₄ film as efficient photoanode for photoelectrochemical water splitting, *Appl. Catal., B*, 2017, **209**, 657–662.
- 134 J. Xu, I. Herraiz-Cardona, X. Yang, S. Gimenez, M. Antonietti and M. Shalom, . The complex role of carbon nitride as a sensitizer in photoelectrochemical cells, *Adv. Opt. Mater.*, 2015, **3**(8), 1052–1058.
- 135 J. Bian, J. Li, S. Kalytchuk, Y. Wang, Q. Li, T. C. Lau, T. A. Niehaus, A. L. Rogach and R.-Q. Zhang, Efficient emission facilitated by multiple energy level transitions in uniform graphitic carbon nitride films deposited by thermal vapor condensation, *ChemPhysChem*, 2015, **16**(5), 954–959.
- 136 Q. Guo, L. Fu, T. Yan, W. Tian, D. Ma, J. Li, Y. Jiang and X. Wang, Improved photocatalytic activity of porous ZnO nanosheets by thermal deposition graphene-like g-C₃N₄ for CO₂ reduction with H₂O vapor, *Appl. Surf. Sci.*, 2020, **509**, 144773.
- 137 Q. Ruan, W. Luo, J. Xie, Y. Wang, X. Liu, Z. Bai, C. J. Carmalt and J. Tang, A nanojunction polymer photoelectrode for efficient charge transport and separation, *Angew. Chem., Int. Ed.*, 2017, **56**(28), 8221–8225.
- 138 J. Bian, C. Huang and R.-Q. Zhang, Graphitic carbon nitride film: an emerging star for catalytic and optoelectronic applications, *ChemSusChem*, 2016, **9**(19), 2723–2735.
- 139 M. Shalom, S. Gimenez, F. Schipper, I. Herraiz-Cardona, J. Bisquert and M. Antonietti, Controlled carbon nitride growth on surfaces for hydrogen evolution electrodes, *Angew. Chem.*, 2014, **126**(14), 3728–3732.
- 140 L. Ye and S. Chen, Fabrication and high visible-light-driven photocurrent response of g-C₃N₄ film: the role of thiourea, *Appl. Surf. Sci.*, 2016, **389**, 1076–1083.
- 141 Y.-S. Jun, E. Z. Lee, X. Wang, W. H. Hong, G. D. Stucky and A. Thomas, From melamine-cyanuric acid supramolecular aggregates to carbon nitride hollow spheres, *Adv. Funct. Mater.*, 2013, **23**(29), 3661–3667.
- 142 J. Xu, T. J. K. Brenner, L. Chabanne, D. Neher, M. Antonietti and M. Shalom., Liquid-based growth of polymeric carbon nitride layers and their use in a mesostructured polymer solar cell with V_{oc} exceeding 1 V, *J. Am. Chem. Soc.*, 2014, **136**(39), 13486–13489.
- 143 R. Cazelles, J. Liu and M. Antonietti, Hybrid C₃N₄/Fluorine-Doped Tin Oxide Electrode Transfers Hydride for 1, 4-NADH Cofactor Regeneration, *ChemElectroChem*, 2015, **2**(3), 333–337.
- 144 J. Liu, H. Wang, Z. P. Chen, H. Moehwald, S. Fiechter, R. van de Krol, L. Wen, L. Jiang and M. Antonietti, Microcontact-printing-assisted access of graphitic carbon nitride films with favorable textures toward photoelectrochemical application, *Adv. Mater.*, 2015, **27**(4), 712–718.
- 145 X. Xie, X. Fan, X. Huang, T. Wang and J. He, *In situ* growth of graphitic carbon nitride films on transparent conducting substrates via a solvothermal route for photoelectrochemical performance, *RSC Adv.*, 2016, **6**(12), 9916–9922.
- 146 Q. Gu, X. Gong, Q. Jia, J. Liu, Z. Gao, X. Wang, J. Long and C. Xue, Compact carbon nitride based copolymer films with controllable thickness for photoelectrochemical water splitting, *J. Mater. Chem. A*, 2017, **5**(36), 19062–19071.
- 147 X. Bai, L. Wang, R. Zong and Y. Zhu, Photocatalytic activity enhanced via g-C₃N₄ nanoplates to nanorods, *J. Phys. Chem. C*, 2013, **117**(19), 9952–9961.
- 148 A. Mehtab, S. M. Alshehri and T. Ahmad, Photocatalytic and photoelectrocatalytic water splitting by porous g-C₃N₄ nanosheets for hydrogen generation, *ACS Appl. Nano Mater.*, 2022, **5**(9), 12656–12665.
- 149 Y. Zhang, A. Thomas, M. Antonietti and X. Wang, Activation of carbon nitride solids by protonation: morphology changes, enhanced ionic conductivity, and photoconduction experiments, *J. Am. Chem. Soc.*, 2009, **131**(1), 50–51.
- 150 Y. Bu, Z. Chen, T. Xie, W. Li and J. P. Ao, Fabrication of C₃N₄ ultrathin flakes by mechanical grind method with enhanced photocatalysis and photoelectrochemical performance, *RSC Adv.*, 2016, **6**(53), 47813–47819.
- 151 G. Peng, J. Albero, H. Garcia and M. Shalom, . A water-splitting carbon nitride photoelectrochemical cell with efficient charge separation and remarkably low onset potential, *Angew. Chem., Int. Ed.*, 2018, **57**(48), 15807–15811.
- 152 N. A. Mohamed, J. Safaei, A. F. Ismail, M. F. Mohamad Noh, N. A. Arzaee, N. N. Mansor, M. A. Ibrahim, N. A. Ludin, J. S. Sagu and M. A. Mat Teridi, Fabrication of exfoliated graphitic carbon nitride, (g-C₃N₄) thin film by methanolic dispersion, *J. Alloys Compd.*, 2020, **818**, 152916.
- 153 J. Qin, J. Barrio, G. Peng, J. Tzadikov, L. Abisdreis, M. Volokh and M. Shalom, . Direct growth of uniform carbon nitride layers with extended optical absorption towards efficient water-splitting photoanodes, *Nat. Commun.*, 2020, **11**(1), 4701.
- 154 B. Guo, L. Tian, W. Xie, A. Batool, G. Xie, Q. Xiang, S. U. Jan, R. Boddula and J. R. Gong, Vertically aligned porous organic semiconductor nanorod array photoanodes for efficient charge utilization, *Nano Lett.*, 2018, **18**(9), 5954–5960.
- 155 Y. Fang, X. Li and X. Wang, Synthesis of polymeric carbon nitride films with adhesive interfaces for solar water splitting devices, *ACS Catal.*, 2018, **8**(9), 8774–8780.
- 156 Y. Fang, X. Li, Y. Wang, C. Giordano and X. Wang, Gradient sulfur doping along polymeric carbon nitride films as visible light photoanodes for the enhanced water oxidation, *Appl. Catal., B*, 2020, **268**, 118398.
- 157 A. E. A. Aboubakr, W. M. A. El Roubi, M. D. Khan, N. Revaprasadu and P. Millet, Effect of morphology and non-metal doping (P and S) on the activity of graphitic carbon nitride toward photoelectrochemical water oxidation, *Sol. Energy Mater. Sol. Cells*, 2021, **232**, 111326.
- 158 S. Vinoth, W. J. Ong and A. Pandikumar, Sulfur-doped graphitic carbon nitride incorporated bismuth oxychloride/



- Cobalt based type-II heterojunction as a highly stable material for photoelectrochemical water splitting, *J. Colloid Interface Sci.*, 2021, **591**, 85–95.
- 159 J. Su, P. Geng, X. Li, Q. Zhao, X. Quan and G. Chen, Novel phosphorus doped carbon nitride modified TiO₂ nanotube arrays with improved photoelectrochemical performance, *Nanoscale*, 2015, **7**(39), 16282–16289.
- 160 W. Kong, X. Zhang, B. Chang, Y. Zhou, S. Zhang, G. He, B. Yang and J. Li, Fabrication of B doped g-C₃N₄/TiO₂ heterojunction for efficient photoelectrochemical water oxidation, *Electrochim. Acta*, 2018, **282**, 767–774.
- 161 N. Lei, J. Li, Q. Song and Z. Liang, Construction of g-C₃N₄/BCN two-dimensional heterojunction photoanode for enhanced photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2019, **44**(21), 10498–10507.
- 162 J. Qin, Y. Jiao, M. Liu, Y. Li and J. Wang, Heat treatment to prepare boron doped g-C₃N₄ nanodots/carbon-rich g-C₃N₄ nanosheets heterojunction with enhanced photocatalytic performance for water splitting hydrogen evolution, *J. Alloys Compd.*, 2022, **898**, 162846.
- 163 S. Vinoth and A. Pandikumar, Ni integrated S-g-C₃N₄/BiOBr based Type-II heterojunction as a durable catalyst for photoelectrochemical water splitting, *Renewable Energy*, 2021, **173**, 507–519.
- 164 P. Chaudhary and P. P. Ingole, Nickel incorporated graphitic carbon nitride supported copper sulfide for efficient noble-metal-free photo-electrochemical water splitting, *Electrochim. Acta*, 2020, **357**, 136798.
- 165 K. N. Mahdi and E. K. Goharshadi, Decoration of graphene oxide as a cocatalyst on Bi doped g-C₃N₄ photoanode for efficient solar water splitting, *J. Electroanal. Chem.*, 2022, **904**, 115933.
- 166 F. Wu, Y. Ma and Y. H. Hu, Near infrared light-driven photoelectrocatalytic water splitting over P-doped g-C₃N₄. ACS Applied Energy, *Materials*, 2020, **3**(11), 11223–11230.
- 167 I. N. Reddy, L. V. Reddy, N. Jayashree, C. V. Reddy, M. Cho, D. Kim and J. Shim, Vanadium-doped graphitic carbon nitride for multifunctional applications: Photoelectrochemical water splitting and antibacterial activities, *Chemosphere*, 2021, **264**, 128593.
- 168 Y. Li, *et al.*, Composite of Cobalt-C₃N₄ on TiO₂ Nanorod Arrays as Co-catalyst for Enhanced Photoelectrochemical Water Splitting, *ChemistrySelect*, 2021, **6**(17), 4319–4329.
- 169 K. N. Mahdi, E. K. Goharshadi and S. J. Mahdizadeh, Efficient photoelectrocatalytic water oxidation by palladium doped g-C₃N₄ electrodeposited thin film, *J. Phys. Chem. C*, 2019, **123**(43), 26106–26115.
- 170 S. Zhao, Y. Zhang, Y. Wang, Y. Zhou, K. Qiu, C. Zhang, J. Fang and X. Sheng, Ionic liquid-assisted synthesis of Br-modified g-C₃N₄ semiconductors with high surface area and highly porous structure for photoredox water splitting, *J. Power Sources*, 2017, **370**, 106–113.
- 171 D. R. Paul, R. Sharma, S. Singh, P. Singh, P. Panchal, A. Sharma, P. Devi and S. P. Nehra, Mg/Li Co-doped g-C₃N₄: An excellent photocatalyst for wastewater remediation and hydrogen production applications towards sustainable development, *Int. J. Hydrogen Energy*, 2023, **48**(96), 37746–37761.
- 172 P. Trogadas, T. F. Fuller and P. Strasser, Carbon as catalyst and support for electrochemical energy conversion, *Carbon*, 2014, **75**, 5–42.
- 173 X. Zhao, D. Pan, X. Chen, R. Li, T. Jiang, W. Wang, G. Li and D. Y. C. Leung, g-C₃N₄ photoanode for photoelectrocatalytic synergistic pollutant degradation and hydrogen evolution, *Appl. Surf. Sci.*, 2019, **467**, 658–665.
- 174 S. Yousefzadeh and B. Fathi, Construction of carbon nanotube-g-C₃N₄ nanocomposite photoanode for the enhanced photoelectrochemical activity in water splitting, *J. Electroanal. Chem.*, 2020, **878**, 114580.
- 175 Y. Wei, Z. Wang, J. Su and L. Guo, Metal-Free Flexible Protonated g-C₃N₄/Carbon Dots Photoanode for Photoelectrochemical Water Splitting, *ChemElectroChem*, 2018, **5**(19), 2734–2737.
- 176 S. S. M. Bhat, S. E. Jun, S. A. Lee, T. H. Lee and H. W. Jang, Influence of C₃N₄ precursors on photoelectrochemical behavior of TiO₂/C₃N₄ photoanode for solar water oxidation, *Energies*, 2020, **13**(4), 974.
- 177 K. Shankar, J. I. Basham, N. K. Allam, O. K. Varghese, G. K. Mor, X. Feng, M. Paulose, J. A. Seabold, K. S. Choi and C. A. Grimes, Recent advances in the use of TiO₂ nanotube and nanowire arrays for oxidative photoelectrochemistry, *J. Phys. Chem. C*, 2009, **113**(16), 6327–6359.
- 178 A. Zhang, M. Zhou, L. Han and Q. Zhou, Combined potential of three catalysis types on TiO₂ nanotube (TNT)/Ti and nanoparticle (TNP)/Ti photoelectrodes: A comparative study, *Appl. Catal., A*, 2010, **385**(1–2), 114–122.
- 179 X. Zhou, B. Jin, L. Li, F. Peng, H. Wang, H. Yu and Y. Fang, A carbon nitride/TiO₂ nanotube array heterojunction visible-light photocatalyst: synthesis, characterization, and photoelectrochemical properties, *J. Mater. Chem.*, 2012, **22**(34), 17900–17905.
- 180 M. Yang, J. Liu, X. Zhang, S. Qiao, H. Huang, Y. Liu and Z. Kang, C₃N₄-sensitized TiO₂ nanotube arrays with enhanced visible-light photoelectrochemical performance, *Phys. Chem. Chem. Phys.*, 2015, **17**(27), 17887–17893.
- 181 L. Wang, W. Si, Y. Ye, S. Wang, F. Hou, X. Hou, H. Cai, S. X. Dou and J. Liang, Cu-ion-implanted and polymeric carbon nitride-decorated TiO₂ nanotube array for unassisted photoelectrochemical water splitting, *ACS Appl. Mater. Interfaces*, 2021, **13**(37), 44184–44194.
- 182 F. Zhang, J. Liu, H. Yue, G. Cheng and X. Xue, Construction of g-C₃N₄ nanoparticles modified TiO₂ nanotube arrays with Z-scheme heterojunction for enhanced photoelectrochemical properties, *J. Mater. Sci.*, 2023, 1–13.
- 183 M. Sun, Y. Fang, Y. Kong, S. Sun, Z. Yu and A. Umar, Graphitic carbon nitride (g-C₃N₄) coated titanium oxide nanotube arrays with enhanced photo-electrochemical performance, *Dalton Trans.*, 2016, **45**(32), 12702–12709.
- 184 C. Liu, F. Wang, J. Zhang, K. Wang, Y. Qiu, Q. Liang and Z. Chen, Efficient photoelectrochemical water splitting by g-C₃N₄/TiO₂ nanotube array heterostructures, *Nano-Micro Lett.*, 2018, **10**, 1–13.
- 185 X. Fan, T. Wang, B. Gao, H. Gong, H. Xue, H. Guo, L. Song, W. Xia, X. Huang and J. He, Preparation of the TiO₂/



- graphic carbon nitride core-shell array as a photoanode for efficient photoelectrochemical water splitting, *Langmuir*, 2016, **32**(50), 13322–13332.
- 186 C. Murugan, K. B. Bhojanaa, W. J. Ong, K. Jothivenkatachalam and A. Pandikumar, Improving hole mobility with the heterojunction of graphitic carbon nitride and titanium dioxide via soft template process in photoelectrocatalytic water splitting, *Int. J. Hydrogen Energy*, 2019, **44**(59), 30885–30898.
- 187 F. Qi, W. An, H. Wang, J. Hu, H. Guo, L. Liu and W. Cui, Combining oxygen vacancies on TiO₂ nanorod arrays with g-C₃N₄ nanosheets for enhancing photoelectrochemical degradation of phenol, *Mater. Sci. Semicond. Process.*, 2020, **109**, 104954.
- 188 L. Xiao, T. Liu, M. Zhang, Q. Li and J. Yang, Interfacial construction of zero-dimensional/one-dimensional g-C₃N₄ nanoparticles/TiO₂ nanotube arrays with Z-scheme heterostructure for improved photoelectrochemical water splitting, *ACS Sustainable Chem. Eng.*, 2018, **7**(2), 2483–2491.
- 189 J. Su, L. Zhu and G. Chen, Ultrasmall graphitic carbon nitride quantum dots decorated self-organized TiO₂ nanotube arrays with highly efficient photoelectrochemical activity, *Appl. Catal., B*, 2016, **186**, 127–135.
- 190 B. Sun, N. Lu, Y. Su, H. Yu, X. Meng and Z. Gao, Decoration of TiO₂ nanotube arrays by graphitic-C₃N₄ quantum dots with improved photoelectrocatalytic performance, *Appl. Surf. Sci.*, 2017, **394**, 479–487.
- 191 L. Huang, Q. Meng, C. Shang, M. Jin, L. Shui, Y. Zhang and Z. Zhang, *et al.*, Modified nanopillar arrays for highly stable and efficient photoelectrochemical water splitting, *Global Challenges*, 2019, **3**(3), 1800027.
- 192 Y. Wang, Y. Zhang, M. Di, L. Fu, H. Pan, K. Zhang and Y. Xu, *et al.*, Realization of ultrathin red 2D carbon nitride sheets to significantly boost the photoelectrochemical water splitting performance of TiO₂ photoanodes, *Chem. Eng. J.*, 2020, **396**, 125267.
- 193 P. Mary Rajaiatha, K. Shamsa, C. Murugan, K. B. Bhojanaa, S. Ravichandran, K. Jothivenkatachalam and A. Pandikumar, Graphitic carbon nitride nanoplatelets incorporated titania based type-II heterostructure and its enhanced performance in photoelectrocatalytic water splitting, *SN Appl. Sci.*, 2020, **2**, 1–14.
- 194 K. Huang, C. Li, X. Zhang, X. Meng, L. Wang, W. Wang and Z. Li, TiO₂ nanorod arrays decorated by nitrogen-doped carbon and g-C₃N₄ with enhanced photoelectrocatalytic activity, *Appl. Surf. Sci.*, 2020, **518**, 146219.
- 195 T. T. Nguyen, H. H. Tran, T. M. Cao and V. V. Pham, Direct fabrication of graphitic carbon nitride-wrapped titanate nanotube arrays toward photoelectrochemical water oxidation in neutral medium, *Korean J. Chem. Eng.*, 2022, **39**(9), 2523–2531.
- 196 Y. Liu, P. Wang, C. Wang and Y. Ao, Polymeric carbon nitride coated Nb-TiO₂ nanorod arrays with enhanced photoelectrocatalytic activity under visible light irradiation, *Inorg. Chem. Commun.*, 2019, **101**, 113–116.
- 197 Y. Ding, S. Maitra, C. Wang, R. Zheng, M. Zhang, T. Barakat and S. Roy, *et al.*, Hydrophilic bi-functional B-doped g-C₃N₄ hierarchical architecture for excellent photocatalytic H₂O₂ production and photoelectrochemical water splitting, *J. Energy Chem.*, 2022, **70**, 236–247.
- 198 P. Kumar, U. K. Thakur, K. Alam, P. Kar, R. Kisslinger, S. Zeng, S. Patel and K. Shankar, Arrays of TiO₂ nanorods embedded with fluorine doped carbon nitride quantum dots (CNFQDs) for visible light driven water splitting, *Carbon*, 2018, **137**, 174–187.
- 199 Y. Li, R. Wang, H. Li, X. Wei, J. Feng, K. Liu, Y. Dang and A. Zhou, Efficient and stable photoelectrochemical seawater splitting with TiO₂@g-C₃N₄ nanorod arrays decorated by Co-Pi, *J. Phys. Chem. C*, 2015, **119**(35), 20283–20292.
- 200 Z. Liu and X. Lu, Multifarious function layers photoanode based on g-C₃N₄ for photoelectrochemical water splitting, *Chin. J. Catal.*, 2018, **39**(9), 1527–1533.
- 201 Y. Li, W. Shang, H. Li, M. Yang, S. Shi, J. Li, C. Huang and A. Zhou, Composite of Cobalt-C₃N₄ on TiO₂ Nanorod Arrays as Co-catalyst for Enhanced Photoelectrochemical Water Splitting, *ChemistrySelect*, 2021, **6**(17), 4319–4329.
- 202 A. K. Rathi, H. Kmentová, A. Naldoni, A. Goswami, M. B. Gawande, R. S. Varma, Š. Kment and R. Zbořil, Significant enhancement of photoactivity in hybrid TiO₂/g-C₃N₄ nanorod catalysts modified with Cu-Ni-based nanostructures, *ACS Appl. Nano Mater.*, 2018, **1**(6), 2526–2535.
- 203 W. Kong, X. Zhang, B. Chang, Y. Guo, Y. Li, S. Zhang and B. Yang, TiO₂ Nanorods Co-decorated with Metal-Free Carbon Materials for Boosted Photoelectrochemical Water Oxidation, *ChemElectroChem*, 2020, **7**(3), 792–799.
- 204 D. Chaudhary, S. Kumar and N. Khare, Boosting the visible-light photoelectrochemical performance of C₃N₄ by coupling with TiO₂ and carbon nanotubes: An organic/inorganic hybrid photocatalyst nanocomposite for photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2020, **45**(55), 30091–30100.
- 205 Z. Yu, Y. Li, J. Qu, R. Zheng, J. M. Cairney, J. Zhang, M. Zhu, A. Khan and W. Li, Enhanced photoelectrochemical water-splitting performance with a hierarchical heterostructure: Co₃O₄ nanodots anchored TiO₂@P-C₃N₄ core-shell nanorod arrays, *Chem. Eng. J.*, 2021, **404**, 126458.
- 206 Y. Liu, Y. X. Yu and W. D. Zhang, Photoelectrochemical study on charge transfer properties of nanostructured Fe₂O₃ modified by g-C₃N₄, *Int. J. Hydrogen Energy*, 2014, **39**(17), 9105–9113.
- 207 X. She, J. Wu, H. Xu, J. Zhong, Y. Wang, Y. Song and K. Nie, *et al.*, High efficiency photocatalytic water splitting using 2D α -Fe₂O₃/g-C₃N₄ Z-scheme catalysts. *Advanced Energy Materials*, 2017, **7**(17), 1700025.
- 208 N. A. Arzaee, M. F. Mohamad Noh, N. S. H. M. Ita, N. A. Mohamed, S. N. Farhana Mohd Nasir, I. N. Nawas Mumthas, A. F. Ismail and M. A. Mat Teridi, Nanostructure-assisted charge transfer in α -Fe₂O₃/g-C₃N₄ heterojunctions for efficient and highly stable photoelectrochemical water splitting, *Dalton Trans.*, 2020, **49**(32), 11317–11328.
- 209 X. An, C. Hu, H. Lan, H. Liu and J. Qu, Strongly coupled metal oxide/reassembled carbon nitride/Co-Pi heterostructures




- for efficient photoelectrochemical water splitting, *ACS Appl. Mater. Interfaces*, 2018, **10**(7), 6424–6432.
- 210 H. Tan, W. Peng, T. Zhang, Y. Han, L. Yin, W. Si, J. Liang and F. Hou, Highly polymerized wine-red carbon nitride to enhance photoelectrochemical water splitting performance of hematite, *J. Phys. Chem. C*, 2021, **125**(24), 13273–13282.
- 211 N. Bhandary, A. P. Singh, P. P. Ingole and S. Basu, Enhancing the photoelectrochemical performance of a hematite dendrite/graphitic carbon nitride nanocomposite through surface modification with CoFeOx, *ChemPhotoChem*, 2017, **1**(2), 70–75.
- 212 P. Arora, A. P. Singh, B. R. Mehta and S. Basu, Metal doped tubular carbon nitride (tC₃N₄) based hematite photoanode for enhanced photoelectrochemical performance, *Vacuum*, 2017, **146**, 570–577.
- 213 S. S. Yi, J. M. Yan and Q. Jiang, Carbon quantum dot sensitized integrated Fe₂O₃@g-C₃N₄ core-shell nanoarray photoanode towards highly efficient water oxidation, *J. Mater. Chem. A*, 2018, **6**(21), 9839–9845.
- 214 A. S. Reddy and J. Kim, An efficient g-C₃N₄-decorated CdS-nanoparticle-doped Fe₃O₄ hybrid catalyst for an enhanced H₂ evolution through photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2020, **513**, 145836.
- 215 T. Annadurai, A. P. Khedulkar, J. Y. Lin, J. Adorna Jr, W. J. Yu, B. Pandit, T. V. Huynh and R. A. Doong, S-scheme N-doped carbon dots anchored g-C₃N₄/Fe₂O₃ shell/core composite for photoelectrocatalytic trimethoprim degradation and water splitting, *Appl. Catal., B*, 2023, **320**, 121928.
- 216 F. Zhan, R. Xie, W. Li, J. Li, Y. Yang, Y. Li and Q. Chen, *In situ* synthesis of g-C₃N₄/WO₃ heterojunction plates array films with enhanced photoelectrochemical performance, *RSC Adv.*, 2015, **5**(85), 69753–69760.
- 217 Y. Li, X. Wei, X. Yan, J. Cai, A. Zhou, M. Yang and K. Liu, Construction of inorganic-organic 2D/2D WO₃/g-C₃N₄ nanosheet arrays toward efficient photoelectrochemical splitting of natural seawater, *Phys. Chem. Chem. Phys.*, 2016, **18**(15), 10255–10261.
- 218 H. Li, F. Zhao, J. Zhang, L. Luo, X. Xiao, Y. Huang, H. Ji and Y. Tong, A g-C₃N₄/WO₃ photoanode with exceptional ability for photoelectrochemical water splitting, *Mater. Chem. Front.*, 2017, **1**(2), 338–342.
- 219 J. Xiao, X. Zhang and Y. Li, A ternary g-C₃N₄/Pt/ZnO photoanode for efficient photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2015, **40**(30), 9080–9087.
- 220 T. J. Park, R. C. Pawar, S. Kang and C. S. Lee, Ultra-thin coating of g-C₃N₄ on an aligned ZnO nanorod film for rapid charge separation and improved photodegradation performance, *RSC Adv.*, 2016, **6**(92), 89944–89952.
- 221 C. Liu, Y. Qiu, F. Wang, K. Wang, Q. Liang and Z. Chen, Design of core-shell-structured ZnO/ZnS hybridized with graphite-like C₃N₄ for highly efficient photoelectrochemical water splitting, *Adv. Mater. Interfaces*, 2017, **4**(21), 1700681.
- 222 Š. Hajduk, S. P. Berglund, M. Podlogar, G. Dražić, F. F. Abdi and Z. C. Orel, and M. Shalom. Conformal Carbon Nitride Coating as an Efficient Hole Extraction Layer for ZnO Nanowires-Based Photoelectrochemical Cells, *Adv. Mater. Interfaces*, 2017, **4**(24), 1700924.
- 223 C. Mahala, M. D. Sharma and M. Basu, ZnO nanosheets decorated with graphite-like carbon nitride quantum dots as photoanodes in photoelectrochemical water splitting, *ACS Appl. Nano Mater.*, 2020, **3**(2), 1999–2007.
- 224 C. Liu, P. Wu, K. Wu, G. Meng, J. Wu, J. Hou, Z. Liu and X. Guo, Advanced bi-functional CoPi co-catalyst-decorated g-C₃N₄ nanosheets coupled with ZnO nanorod arrays as integrated photoanodes, *Dalton Trans.*, 2018, **47**(18), 6605–6614.
- 225 M. Sun, Z. Chen, X. Jiang, C. Feng and R. Zeng, Optimized preparation of Co-Pi decorated g-C₃N₄@ ZnO shell-core nanorod array for its improved photoelectrochemical performance and stability, *J. Alloys Compd.*, 2019, **780**, 540–551.
- 226 C. Liu, Y. Qiu, J. Zhang, Q. Liang, N. Mitsuzaki and Z. Chen, Construction of CdS quantum dots modified g-C₃N₄/ZnO heterostructured photoanode for efficient photoelectrochemical water splitting, *J. Photochem. Photobiol., A*, 2019, **371**, 109–117.
- 227 Z. Masoumi, M. Tayebi, M. Kolaei and B. K. Lee, Improvement of surface light absorption of ZnO photoanode using a double heterojunction with α -Fe₂O₃/g-C₃N₄ composite to enhance photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2023, **608**, 154915.
- 228 H. Bian, A. Wang, Z. Li, Z. Li, Y. Diao, J. Lu and Y. Y. Li, g-C₃N₄-Modified Water-Crystallized Mesoporous SnO₂ for Enhanced Photoelectrochemical Properties, *Part. Part. Syst. Charact.*, 2018, **35**(10), 1800155.
- 229 B. Babu, R. Koutavarapu, J. Shim and K. Yoo, Enhanced visible-light-driven photoelectrochemical and photocatalytic performance of Au-SnO₂ quantum dot-anchored g-C₃N₄ nanosheets, *Sep. Purif. Technol.*, 2020, **240**, 116652.
- 230 P. Chaudhary and P. P. Ingole, In-Situ solid-state synthesis of 2D/2D interface between Ni/NiO hexagonal nanosheets supported on g-C₃N₄ for enhanced photo-electrochemical water splitting, *Int. J. Hydrogen Energy*, 2020, **45**(32), 16060–16070.
- 231 U. Baig, A. Khan, M. A. Gondal, M. A. Dastageer and W. S. Falath, Laser induced anchoring of nickel oxide nanoparticles on polymeric graphitic carbon nitride sheets using pulsed laser ablation for efficient water splitting under visible light, *Nanomaterials*, 2020, **10**(6), 1098.
- 232 H. Hao, D. Lu and Q. Wang, Photoelectrochemical study on charge separation mechanisms of Bi₂WO₆ quantum dots decorated g-C₃N₄, *Int. J. Hydrogen Energy*, 2018, **43**(18), 8824–8834.
- 233 C. Murugan, K. Ranjithkumar and A. Pandikumar, Interfacial charge dynamics in type-II heterostructured sulfur doped-graphitic carbon nitride/bismuth tungstate as competent photoelectrocatalytic water splitting photoanode, *J. Colloid Interface Sci.*, 2021, **602**, 437–451.
- 234 Y. Wang, Y. Tian, L. Yan and Z. Su, DFT study on sulfur-doped g-C₃N₄ nanosheets as a photocatalyst for CO₂ reduction reaction, *J. Phys. Chem. C*, 2018, **122**(14), 7712–7719.



- 235 C. V. Reddy, R. Koutavarapu, I. N. Reddy and J. Shim, Effect of a novel one-dimensional zinc tungsten oxide nanorods anchored two-dimensional graphitic carbon nitride nanosheets for improved solar-light-driven photocatalytic removal of toxic pollutants and photoelectrochemical water splitting, *J. Mater. Sci.: Mater. Electron.*, 2021, **32**, 33–46.
- 236 C. Murugan, R. A. Nataraj, M. P. Kumar, S. Ravichandran and A. Pandikumar, Enhanced Charge Transfer Process of Bismuth Vanadate Interleaved Graphitic Carbon Nitride Nanohybrids in Mediator-Free Direct Z Scheme Photoelectrocatalytic Water Splitting, *ChemistrySelect*, 2019, **4**(16), 4653–4663.
- 237 P. Mane, H. Bae, V. Burungale, S. W. Lee, M. Misra, H. Parbat, A. N. Kadam and J. S. Ha, Interface-engineered Z-scheme of BiVO₄/g-C₃N₄ photoanode for boosted photoelectrochemical water splitting and organic contaminant elimination under solar light, *Chemosphere*, 2022, **308**, 136166.
- 238 M. F. R. Samsudin, H. Ullah, R. Bashiri, N. M. Mohamed, S. Sufian and Y. H. Ng, Experimental and DFT insights on microflower g-C₃N₄/BiVO₄ photocatalyst for enhanced photoelectrochemical hydrogen generation from lake water, *ACS Sustainable Chem. Eng.*, 2020, **8**(25), 9393–9403.
- 239 B. Zhang, S. Y. Zhao, H. H. Wang, T. J. Zhao, Y. X. Liu, L. B. Lv, X. Wei, X. H. Li and J. S. Chen, The solution-phase process of a g-C₃N₄/BiVO₄ dyad to a large-area photoanode: interfacial synergy for highly efficient water oxidation, *Chem. Commun.*, 2017, **53**(76), 10544–10547.
- 240 C. Feng, Z. Wang, Y. Ma, Y. Zhang, L. Wang and Y. Bi, Ultrathin graphitic C₃N₄ nanosheets as highly efficient metal-free cocatalyst for water oxidation, *Appl. Catal., B*, 2017, **205**, 19–23.
- 241 G. Zeng, X. Wang, X. Yu, J. Guo, Y. Zhu and Y. Zhang, Ultrathin g-C₃N₄/Mo:BiVO₄ photoanode for enhanced photoelectrochemical water oxidation, *J. Power Sources*, 2019, **444**, 227300.
- 242 K. H. Ye, H. Li, D. Huang, S. Xiao, W. Qiu, M. Li, Y. Hu, W. Mai, H. Ji and S. Yang, Enhancing photoelectrochemical water splitting by combining work function tuning and heterojunction engineering, *Nat. Commun.*, 2019, **10**(1), 3687.
- 243 N. A. Mohamed, H. Ullah, J. Safaei, A. F. Ismail, M. F. Mohamad Noh, M. F. Soh, M. A. Ibrahim, N. A. Ludin and M. A. Mat Teridi, Efficient photoelectrochemical performance of γ irradiated g-C₃N₄ and its g-C₃N₄ @ BiVO₄ heterojunction for solar water splitting, *J. Phys. Chem. C*, 2019, **123**(14), 9013–9026.
- 244 T. Jiang, F. Nan, J. Zhou, F. Zheng, Y. Weng, T. Y. Cai, S. Ju, B. Xu and L. Fang, Enhanced photocatalytic and photoelectrochemical performance of g-C₃N₄/BiVO₄ heterojunction: A combined experimental and theoretical study, *AIP Adv.*, 2019, **9**(5), 055225.
- 245 J. Prakash, U. Prasad, R. Alexander, J. Bahadur, K. Dasgupta and A. N. Mada Kannan, Photoelectrochemical solar water splitting: the role of the carbon nanomaterials in bismuth vanadate composite photoanodes toward efficient charge separation and transport, *Langmuir*, 2019, **35**(45), 14492–14504.
- 246 D. Sariket, D. Ray, S. Baduri, S. Ghosh, A. Maity and C. Bhattacharya, Synthesis of g-C₃N₄/InVO₄ Semiconductor for Improved Photocatalytic and Photoelectrochemical Applications, *Electroanalysis*, 2020, **32**(11), 2535–2544.
- 247 Y. Li, G. Liu, D. Jia, C. Li, L. Wang, J. Zheng, X. Liu and Z. Jiao, Nanoporous FeVO₄ Photoanodes Modified with Ultrathin C₃N₄ for High Photoelectrochemical Water Splitting Performance, *Catal. Lett.*, 2019, **149**, 19–24.
- 248 Y. Cao, Roadmap and direction toward high-performance MoS₂ hydrogen evolution catalysts, *ACS Nano*, 2021, **15**(7), 11014–11039.
- 249 X. Hu, X. Zeng, Y. Liu, J. Lu, S. Yuan, Y. Yin, J. Hu, D. T. McCarthy and X. Zhang, Nano-layer based 1T-rich MoS₂/g-C₃N₄ co-catalyst system for enhanced photocatalytic and photoelectrochemical activity, *Appl. Catal., B*, 2020, **268**, 118466.
- 250 L. Ge, C. Han, X. Xiao and L. Guo, Synthesis and characterization of composite visible light active photocatalysts MoS₂-g-C₃N₄ with enhanced hydrogen evolution activity, *Int. J. Hydrogen Energy*, 2013, **38**(17), 6960–6969.
- 251 L. Ye, D. Wang and S. Chen, Fabrication and enhanced photoelectrochemical performance of MoS₂/S-doped g-C₃N₄ heterojunction film, *ACS Appl. Mater. Interfaces*, 2016, **8**(8), 5280–5289.
- 252 L. Ye, H. Zhang, Y. Xiong, C. Kong, H. Li and W. Li, Efficient photoelectrochemical overall water-splitting of MoS₂/g-C₃N₄ n-n type heterojunction film, *J. Chem. Phys.*, 2021, **154**(21), 214701.
- 253 P. Subramanyam, B. Meena, D. Suryakala, M. Deepa and C. Subrahmanyam, Plasmonic nanometal decorated photoanodes for efficient photoelectrochemical water splitting, *Catal. Today*, 2021, **379**, 1–6.
- 254 S. B. Kokane, R. Sasikala, D. M. Phase and S. D. Sartale, In₂S₃ nanoparticles dispersed on g-C₃N₄ nanosheets: role of heterojunctions in photoinduced charge transfer and photoelectrochemical and photocatalytic performance, *J. Mater. Sci.*, 2017, **52**, 7077–7090.
- 255 M. D. Sharma and M. Basu, Nanosheets of In₂S₃/S-C₃N₄-Dots for Solar Water-Splitting in Saline Water, *Langmuir*, 2022, **38**(42), 12981–12990.
- 256 R. Wang, J. Yan, M. Zu, S. Yang, X. Cai, Q. Gao, Y. Fang, S. Zhang and S. Zhang, Facile synthesis of interlocking g-C₃N₄/CdS photoanode for stable photoelectrochemical hydrogen production, *Electrochim. Acta*, 2018, **279**, 74–83.
- 257 T. Mahvelati-Shamsabadi, E. K. Goharshadi and M. Karimi-Nazarabad, Z-scheme design of Ag@g-C₃N₄/ZnS photoanode device for efficient solar water oxidation: An organic-inorganic electronic interface, *Int. J. Hydrogen Energy*, 2019, **44**(26), 13085–13097.
- 258 C. He, J. H. Zhang, W. X. Zhang and T. T. Li, Type-II InSe/g-C₃N₄ heterostructure as a high-efficiency oxygen evolution reaction catalyst for photoelectrochemical water splitting, *J. Phys. Chem. Lett.*, 2019, **10**(11), 3122–3128.



- 259 S. J. Kim, Y. Lee, D. K. Lee, J. W. Lee and J. K. Kang, Efficient Co-Fe layered double hydroxide photocatalysts for water oxidation under visible light, *J. Mater. Chem. A*, 2014, **2**(12), 4136–4139.
- 260 W. Lin and H. Frei, Photochemical CO₂ splitting by metal-to-metal charge-transfer excitation in mesoporous ZrCu (I)-MCM-41 silicate sieve, *J. Am. Chem. Soc.*, 2005, **127**(6), 1610–1611.
- 261 Y. Hou, Z. Wen, S. Cui, X. Feng and J. Chen, Strongly coupled ternary hybrid aerogels of N-deficient porous graphitic-C₃N₄ nanosheets/N-doped graphene/NiFe-layered double hydroxide for solar-driven photoelectrochemical water oxidation, *Nano Lett.*, 2016, **16**(4), 2268–2277.
- 262 M. Arif, G. Yasin, M. Shakeel, X. Fang, R. Gao, S. Ji and D. Yan, Coupling of bifunctional CoMn-layered double hydroxide@graphitic C₃N₄ nanohybrids towards efficient photoelectrochemical overall water splitting, *Chem. – Asian J.*, 2018, **13**(8), 1045–1052.
- 263 M. Arif, G. Yasin, M. Shakeel, M. A. Mushtaq, W. Ye, X. Fang, S. Ji and D. Yan, Hierarchical CoFe-layered double hydroxide and g-C₃N₄ heterostructures with enhanced bifunctional photo/electrocatalytic activity towards overall water splitting, *Mater. Chem. Front.*, 2019, **3**(3), 520–531.
- 264 X. Fan, T. Wang, B. Gao, X. Xie, S. Zhang, X. Meng, H. Gong, Y. Guo, X. Huang and J. He, Layered double hydroxides decorated graphitic carbon nitride film as efficient photoanodes for photoelectrochemical water splitting, *Catal. Today*, 2019, **335**, 423–428.
- 265 S. Nayak and K. M. Parida, Deciphering Z-scheme charge transfer dynamics in heterostructure NiFe-LDH/N-rGO/g-C₃N₄ nanocomposite for photocatalytic pollutant removal and water splitting reactions, *Sci. Rep.*, 2019, **9**(1), 2458.
- 266 S. Guru, S. Kumar, S. Bellamkonda and R. R. Gangavarapu, Synthesis of CuTi-LDH supported on g-C₃N₄ for electrochemical and photoelectrochemical oxygen evolution reactions, *Int. J. Hydrogen Energy*, 2021, **46**(30), 16414–16430.
- 267 S. Guru, Bismuth oxycarbonate grafted NiFe-LDH supported on g-C₃N₄ as bifunctional catalyst for photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2021, **46**(22), 12145–12157.
- 268 K. N. Mahdi, E. K. Goharshadi and H. S. Sajjadizadeh, Copper-Azolate Framework Coated on g-C₃N₄ Nanosheets as a Core-Shell Heterojunction and Decorated with a Ni(OH)₂ Cocatalyst for Efficient Photoelectrochemical Water Splitting, *J. Phys. Chem. C*, 2022, **126**(19), 8327–8336.
- 269 R. Cao, H. Yang, S. Zhang and X. Xu, Engineering of Z-scheme 2D/3D architectures with Ni(OH)₂ on 3D porous g-C₃N₄ for efficiently photocatalytic H₂ evolution, *Appl. Catal., B*, 2019, **258**, 117997.
- 270 V. Selvaraj and A. Pandikumar, Turning UV light-active BiOF into visible light-active BiOF by forming a heterojunction with g-C₃N₄ and its photoelectrochemical water splitting performance in reverse osmosis-rejected wastewater, *J. Phys. Chem. C*, 2021, **126**(1), 79–90.
- 271 S. Vinoth, P. M. Rajaitha and A. Pandikumar, Modulating photoelectrochemical water splitting performance by constructing a type-II heterojunction between g-C₃N₄ and BiOI, *New J. Chem.*, 2021, **45**(4), 2010–2018.
- 272 P. Velusamy, X. Liu, M. Sathiyaa, N. S. Alsaiani, F. M. Alzahrani, M. T. Nazir, E. Elamurugu, M. Senthil Pandian and F. Zhang, Investigate the suitability of g-C₃N₄ nanosheets ornamented with BiOI nanoflowers for photocatalytic dye degradation and PEC water splitting, *Chemosphere*, 2023, 138007.
- 273 P. Velusamy, M. Sathiyaa, Y. Liu, S. Liu, R. Ramesh Babu, M. A. Saad Aly, E. Elangovan, H. Chang, L. Mao and R. Xing, Investigating the effect of Nd³⁺ dopant and the formation of g-C₃N₄/BiOI heterostructure on the microstructural, optical and photoelectrocatalytic properties of g-C₃N₄, *Appl. Surf. Sci.*, 2021, **561**, 150082.
- 274 Y. Ma, Z. Wang, Y. Jia, L. Wang, M. Yang, Y. Qi and Y. Bi, Bi₂MoO₆ nanosheet array modified with ultrathin graphitic carbon nitride for high photoelectrochemical performance, *Carbon*, 2017, **114**, 591–600.
- 275 J. Li, H. Yuan and Z. Zhu, Improved photoelectrochemical performance of Z-scheme g-C₃N₄/Bi₂O₃/BiPO₄ heterostructure and degradation property, *Appl. Surf. Sci.*, 2016, **385**, 34–41.
- 276 N. A. Mohamed, A. F. Ismail, J. Safaei, M. R. Johan and M. A. Mat Teridi, A novel photoanode based on Thorium oxide (ThO₂) incorporated with graphitic Carbon nitride (g-C₃N₄) for Photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2021, **569**, 151043.
- 277 Y. Zheng, Q. Ruan, J. X. Ren, X. Guo, Y. Zhou, B. Zhou, Q. Xu, Q. Fu, S. Wang and Y. Huang, Plasma-assisted liquid-based growth of g-C₃N₄/Mn₂O₃ pn heterojunction with tunable valence band for photoelectrochemical application, *Appl. Catal., B*, 2023, **323**, 122170.
- 278 N. Bhandary, A. P. Singh, S. Kumar, P. P. Ingole, G. S. Thakur, A. K. Ganguli and S. Basu, In situ solid-state synthesis of a AgNi/g-C₃N₄ nanocomposite for enhanced photoelectrochemical and photocatalytic activity, *ChemSusChem*, 2016, **9**(19), 2816–2823.
- 279 Z. Chen, G. Ma, Z. Chen, Y. Zhang, Z. Zhang, J. Gao and Q. Meng, *et al.*, Fabrication and photoelectrochemical properties of silicon nanowires/g-C₃N₄ core/shell arrays, *Appl. Surf. Sci.*, 2017, **396**, 609–615.
- 280 U. Baig, A. Khan, M. A. Gondal, M. A. Dastageer and S. Akhtar, Single-step synthesis of silicon carbide anchored graphitic carbon nitride nanocomposite photo-catalyst for efficient photoelectrochemical water splitting under visible-light irradiation, *Colloids Surf., A*, 2021, **611**, 125886.
- 281 Z. Huang, X. Zeng, K. Li, S. Gao, Q. Wang and J. Lu, Z-scheme NiTiO₃/g-C₃N₄ heterojunctions with enhanced photoelectrochemical and photocatalytic performances under visible LED light irradiation, *ACS Appl. Mater. Interfaces*, 2017, **9**(47), 41120–41125.
- 282 Y. Liu, J. Zhang, X. Li, Z. Yao, L. Zhou, H. Sun and S. Wang, Graphitic carbon nitride decorated with CoP nanocrystals for enhanced photocatalytic and photoelectrochemical H₂ evolution, *Energy Fuels*, 2019, **33**(11), 11663–11676.
- 283 Y. Liu, X. Li, H. He, S. Yang, G. Jia and S. Liu, CoP imbedded g-C₃N₄ heterojunctions for highly efficient



- photo, electro and photoelectrochemical water splitting, *J. Colloid Interface Sci.*, 2021, **599**, 23–33.
- 284 M. M. Islam, R. D. Tentu and S. Basu, Synthesis of g-C₃N₄/ZnGa_{1.9}Al_{0.1}O₄ Heterojunction Using Narrow and Wide Band Gap Material for Enhanced Photoelectrochemical Water Splitting, *ChemistrySelect*, 2018, **3**(2), 486–494.
- 285 J. Hou, H. Cheng, O. Takeda and H. Zhu, Unique 3D heterojunction photoanode design to harness charge transfer for efficient and stable photoelectrochemical water splitting, *Energy Environ. Sci.*, 2015, **8**(4), 1348–1357.
- 286 X. Xu, Y. Liu, Y. Zhu, X. Fan, Y. Li, F. Zhang, G. Zhang and W. Peng, Fabrication of a Cu₂O/g-C₃N₄/WS₂ Triple-Layer Photocathode for Photoelectrochemical Hydrogen Evolution, *ChemElectroChem*, 2017, **4**(6), 1498–1502.
- 287 X. Ma, J. Zhang, B. Wang, Q. Li and S. Chu, Hierarchical Cu₂O foam/g-C₃N₄ photocathode for photoelectrochemical hydrogen production, *Appl. Surf. Sci.*, 2018, **427**, 907–916.
- 288 R. S. Moakhar, F. Soleimani, S. K. Sadrnezhaad, S. Masudypanah, R. Katal, A. Seza, N. Ghane and S. Ramakrishna, One-pot microwave synthesis of hierarchical C-doped CuO dandelions/g-C₃N₄ nanocomposite with enhanced photostability for photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2020, **530**, 147271.
- 289 V. Ragupathi, M. A. Raja, P. Panigrahi and N. G. Subramaniam, CuO/g-C₃N₄ nanocomposite as promising photocatalyst for photoelectrochemical water splitting, *Optik*, 2020, **208**, 164569.
- 290 Q. Huang, Z. Ye and X. Xiao, Recent progress in photocathodes for hydrogen evolution, *J. Mater. Chem. A*, 2015, **3**(31), 15824–15837.
- 291 P. P. Kunturu and J. Huskens, Improving Charge Separation in Cu₂O/g-C₃N₄/CoS Photocathodes by a Z-Scheme Heterojunction to Achieve Enhanced Performance and Photostability, *Clean Energy Materials*, American Chemical Society, 2020, pp. 111–136.
- 292 F. Yang, V. Kuznietsov, M. Lublow, C. Merschjann, A. Steigert, J. Klaer, A. Thomas and T. Schedel-Niedrig, Solar hydrogen evolution using metal-free photocatalytic polymeric carbon nitride/CuInS₂ composites as photocathodes, *J. Mater. Chem. A*, 2013, **1**(21), 6407–6415.
- 293 D. Wang, C. Wang, F. P. Garcia de Arquer, J. Zhong, L. Qian, L. Fang and P. Liu, *et al.*, Band-aligned C₃N₄-xS_{3x/2} stabilizes CdS/CuInGaS₂ photocathodes for efficient water reduction, *J. Mater. Chem. A*, 2017, **5**(7), 3167–3171.
- 294 Z. Wang, B. Jin, G. Zou, K. Zhang, X. Hu and J. H. Park, Rationally Designed Copper-Modified Polymeric Carbon Nitride as a Photocathode for Solar Water Splitting, *ChemSusChem*, 2019, **12**(4), 866–872.
- 295 Y. Zhang, Z. Schnepp, J. Cao, S. Ouyang, Y. Li, J. Ye and S. Liu, Biopolymer-activated graphitic carbon nitride towards a sustainable photocathode material, *Sci. Rep.*, 2013, **3**(1), 2163.
- 296 J. Wang, F. Y. Su and W. D. Zhang, Preparation and enhanced visible light photoelectrochemical activity of g-C₃N₄/ZnO nanotube arrays, *J. Solid State Electrochem.*, 2014, **18**, 2921–2929.
- 297 Y. Dong, Y. Chen, P. Jiang, G. Wang, X. Wu and R. Wu, A novel g-C₃N₄ based photocathode for photoelectrochemical hydrogen evolution, *RSC Adv.*, 2016, **6**(9), 7465–7473.
- 298 M.-Y. Ye, Z.-H. Zhao, Z.-F. Hu, L.-Q. Liu, H.-M. Ji, Z.-R. Shen and T.-Y. Ma, 0D/2D heterojunctions of vanadate quantum dots/graphitic carbon nitride nanosheets for enhanced visible-light-driven photocatalysis, *Angew. Chem., Int. Ed.*, 2017, **56**(29), 8407–8411.
- 299 G. S. Shanker, R. Bhosale, S. Ogale and A. Nag, 2D Nanocomposite of g-C₃N₄ and TiN Embedded N-Doped Graphene for Photoelectrochemical Reduction of Water Using Sunlight, *Adv. Mater. Interfaces*, 2018, **5**(24), 1801488.
- 300 Y.-Y. Han, X.-L. Lu, S.-F. Tang, X.-P. Yin, Z.-W. Wei and T.-B. Lu, Metal-free 2D/2D heterojunction of graphitic carbon nitride/graphdiyne for improving the hole mobility of graphitic carbon nitride. *Advanced Energy Materials*, 2018, **8**(16), 1702992.
- 301 S. Gopalakrishnan, G. M. Bhalerao and K. Jeganathan, SrTiO₃ NPs/g-C₃N₄ NSs coupled Si NWs based hybrid photocathode for visible light driven photoelectrochemical water reduction, *ACS Sustainable Chem. Eng.*, 2019, **7**(16), 13911–13919.
- 302 G. S. Shanker, R. A. Panchal, S. Ogale and A. Nag, g-C₃N₄:Sn-doped In₂O₃ (ITO) nanocomposite for photoelectrochemical reduction of water using solar light, *J. Solid State Chem.*, 2020, **285**, 121187.
- 303 S. Wang, F. Nan, Y. Zhou, F. Zheng, Y. Weng, L. You and L. Fang, Enhanced photoelectrochemical performance in BiFeO₃/g-C₃N₄ p-n heterojunction photocathodes with ferroelectric polarization, *J. Appl. Phys.*, 2020, **128**(15), 154101.
- 304 S. Wang, F. Zheng, Y. Weng, G. Yuan, L. Fang and L. You, Enhanced Photoelectrochemical Performance by Interface Engineering in Ternary g-C₃N₄/TiO₂/PbTiO₃ Films, *Adv. Mater. Interfaces*, 2020, **7**(10), 2000185.
- 305 V. Guigoz, L. Balan, A. Aboulaich, R. Schneider and T. Gries, Heterostructured thin LaFeO₃/g-C₃N₄ films for efficient photoelectrochemical hydrogen evolution, *Int. J. Hydrogen Energy*, 2020, **45**(35), 17468–17479.
- 306 E. Sitara, H. Nasir, A. Mumtaz, M. F. Ehsan, M. Sohail, S. Iram, S. A. Batool Bukhari, S. Ullah, T. Akhtar and A. Iqbal, Enhanced photoelectrochemical water splitting using zinc selenide/graphitic carbon nitride type-II heterojunction interface, *Int. J. Hydrogen Energy*, 2021, **46**(50), 25424–25435.
- 307 P. Babu, H. Kim, J. Y. Park and B. Naik, Trioctylphosphine Oxide (TOPO)-Assisted Facile Fabrication of Phosphorus-Incorporated Nanostructured Carbon Nitride Toward Photoelectrochemical Water Splitting with Enhanced Activity, *Inorg. Chem.*, 2022, **61**(3), 1368–1376.

