



Cite this: *J. Mater. Chem. C*, 2022, 10, 2095

## Coordination units of $\text{Mn}^{2+}$ modulation toward tunable emission in zero-dimensional bromides for white light-emitting diodes†

Guojun Zhou,<sup>‡\*a</sup> Jialiang Ding,<sup>‡a</sup> Xingxing Jiang,<sup>‡b</sup> Jian Zhang,<sup>‡a</sup> Maxim S. Molokeev,<sup>‡cde</sup> Qiqiong Ren,<sup>a</sup> Jun Zhou,<sup>‡f</sup> Shili Li<sup>a</sup> and Xian-Ming Zhang<sup>‡\*ag</sup>

Organic–inorganic metal halides have become a multifunctional platform for manipulating photoluminescence due to highly efficient and tunable emissions, especially for lead-free  $\text{Mn}^{2+}$ -based halides. Herein, the zero-dimensional (0D) bromides of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  with different coordination environments were designed and synthesized by a solvent evaporation method. They exhibit green and red broadband emission peaks at 528 nm and 627 nm with high photoluminescence quantum yields of 86.83% and 61.91%, respectively, which are attributed to the d–d transition ( ${}^4\text{T}_1(\text{G}) \rightarrow {}^6\text{A}_1(\text{S})$ ) of  $[\text{MnBr}_4]^{2-}$  tetrahedral and  $[\text{Mn}_2\text{Br}_{12}]^{6-}$  octahedral units. The cases emphasize the effect of organic ligands on the intrinsic emissions of  $\text{Mn}^{2+}$  ions, thereby revealing the luminescence mechanism of  $\text{Mn}^{2+}$  ions in 0D isolated structures through the Tanabe–Sugano (TS) energy diagram. Thanks to their bright and stable emissions, the fabricated white light-emitting diode (LED) based on  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  provides an outstanding color rendering index ( $R_a$ ) of 90.8 at a correlated color temperature (CCT) of 3709 K, along with the CIE chromaticity coordinates of (0.3985, 0.3979) and a luminous efficacy of 51.2  $\text{lm W}^{-1}$ . This work aims at clarifying the relationship between the coordination units of  $\text{Mn}^{2+}$  and tunable emissions, and in particular, proposes a new strategy to explore phosphors excited by blue light for white LEDs.

Received 25th November 2021,  
Accepted 6th January 2022

DOI: 10.1039/d1tc05680h

rsc.li/materials-c

## 1. Introduction

Organic–inorganic metal halides (OIMHs) formed by self-assembly of organic cations and inorganic anions have received extensive interest in many fields, such as light-emitting diodes (LEDs), photodetectors, ferroelectrics, solar cells, and so on.<sup>1–6</sup> Compared to all-inorganic metal halides, OIMHs have a high degree of design flexibility owing to the various structural dimensions and abundant chemical components.<sup>7–9</sup> Among them, as a kind of hybrid material composed of organic cations and spatially isolated anions, zero-dimensional (0D) OIMHs provide an excellent platform for the development of high-efficiency emitting materials,<sup>10–12</sup> in particular, 0D  $\text{Mn}^{2+}$ -based OIMHs have attracted much attention.<sup>13–16</sup>

Although most of the reported OIMHs possess excellent luminescence properties, the toxicity of  $\text{Pb}^{2+}$  and instability limit their practical applications, which lead to the development of lead-free OIMHs becoming imminent.<sup>17–20</sup> In comparison, the  $\text{Mn}^{2+}$ -based OIMHs present the advantages of environmental friendliness, good stability and tunable emission. As is well known the transition metal ion  $\text{Mn}^{2+}$  has a  $3d^5$  electronic configuration and generally exhibits visible (vis) photoluminescence (PL) originating from the  ${}^4\text{T}_1 \rightarrow {}^6\text{A}_1$  transition, which

<sup>a</sup> Key Laboratory of Magnetic Molecules and Magnetic Information Materials (Ministry of Education), School of Chemistry and Material Science, Shanxi Normal University, Taiyuan 030006, China. E-mail: zhougj@sxnu.edu.cn, zhangxm@dns.sxnu.edu.cn; Tel: +86-0357-2051402

<sup>b</sup> China Technical Institute of Physics and Chemistry, Chinese Academy of Sciences, Beijing 100190, China

<sup>c</sup> Laboratory of Crystal Physics, Kirensky Institute of Physics, Federal Research Center KSC SB RAS, Krasnoyarsk 660036, Russia

<sup>d</sup> Department of Engineering Physics and Radioelectronics, Siberian Federal University, Krasnoyarsk 660041, Russia

<sup>e</sup> Research and Development Department, Kemerovo State University, Kemerovo, 650000, Russia

<sup>f</sup> Department of Physics, Beijing Technology and Business University, Beijing 100048, China

<sup>g</sup> College of Chemistry & Chemical Engineering, Key Laboratory of Interface Science and Engineering in Advanced Material, Ministry of Education, Taiyuan University of Technology, Taiyuan, Shanxi 030024, P. R. China

† Electronic supplementary information (ESI) available: Fig. S1–S5 showing PXRD patterns, FTIR spectra, UV-visible absorption spectra, thermogravimetric (TG) curves, and temperature-dependent PL spectra of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ ; Table S1 listing fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters. Table S2 listing the main bond lengths. Table S3 listing hydrogen-bond geometry in the structures. Crystallographic data of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (CIF). CCDC 2094640 and 2094641. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d1tc05680h

‡ These authors contributed equally.

strongly depends on the crystal field surroundings of  $\text{Mn}^{2+}$  in the host lattice.<sup>21,22</sup> Octahedrally coordinated  $\text{Mn}^{2+}$  shows an orange to red emission with a large full width at half maximum (FWHM > 60 nm), while tetrahedrally coordinated  $\text{Mn}^{2+}$  exhibits a green-yellow emission (500–550 nm) with a small FWHM of 25–60 nm.<sup>23–27</sup> So far,  $\text{Mn}^{2+}$ -doped metal halides with orange-red emissions have been reported the most,<sup>28–34</sup> but unfortunately, they cannot be well applied in the field of solid-state lighting due to the shortcoming that almost all of them cannot be excited by blue light, resulting in a low efficiency for white LED devices. Most of the  $\text{Mn}^{2+}$ -based OIMHs exhibit a narrow-band green emission.<sup>13–15,35–39</sup> Even if these 0D analogues show a high-efficiency  $\text{Mn}^{2+}$  emission with near-unity photoluminescence quantum yields (PLQYs), the relatively small FWHM (20–60 nm) of the PL peak makes it impossible to endow high-performance white LED devices with a high color rendering index ( $R_a$ ) for the application of solid-state lighting.<sup>40,41</sup> In addition, the 0D  $\text{Mn}^{2+}$ -based OIMHs with a highly efficient red emission have also been reported and popularized recently. However, only a small amount of 0D  $\text{Mn}^{2+}$ -based OIMHs that can emit red light was investigated so far,<sup>3,24,42,43</sup> and there is no comparative analysis of their luminescence mechanism by binding to that of 0D  $\text{Mn}^{2+}$ -based OIMHs with green light emission.

Organic ligands, as a key component to modify  $\text{Mn}^{2+}$  coordination units in OIMHs, play an irreplaceable role in the construction of their electronic band structures and crystal structures. In this work, we employed organic cations including guanidine hydrobromide and 1,1,3,3-tetramethylguanidine hydrobromide, and synthesized two kinds of 0D  $\text{Mn}^{2+}$ -based bromides with broadband emission by reacting them with  $\text{MnBr}_2$  respectively. Efficient room-temperature phosphorescence originating from the d–d transition ( $^4\text{T}_1\text{--}^6\text{A}_1$ ) of  $\text{Mn}^{2+}$  is demonstrated in these compounds and shows a strong dependence on the crystal field surroundings of  $\text{Mn}^{2+}$ . Furthermore, we elaborated the electronic features and optical absorption according to the Tanabe–Sugano (TS) diagram of the  $3d^5$  electron orbital of  $\text{Mn}^{2+}$  and extended the principle by employing organic ligands to tune the  $\text{Mn}^{2+}$  emission in 0D bromides. The as-fabricated white LED device with a high  $R_a$  of 90.8 at a correlated color temperature (CCT) of 3709 K demonstrates that  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  can be promising as rare-earth-free and lead-free phosphors in the field of solid-state lighting. Our realizable cases provide a deep understanding about the coordination units of  $\text{Mn}^{2+}$  toward tunable emission and propose a new way to explore high-performance OIMHs pumped by blue light for white LEDs.

## 2. Experimental section

### 2.1 Materials and preparation

Guanidine hydrobromide ( $\text{CH}_6\text{N}_3\text{Br}$ , 98%, Sigma-Aldrich), 1,1,3,3-tetramethylguanidine ( $\text{C}_5\text{H}_{13}\text{N}_3$ , 98%, Energy chemical), manganese bromide tetrahydrate ( $\text{MnBr}_2 \cdot 4\text{H}_2\text{O}$ , 98%, Aladdin), hydrobromic acid (HBr, 40%, Aladdin), acetonitrile ( $\text{CH}_3\text{CN}$ , 99.5%, Kermel) and ethanol ( $\text{C}_2\text{H}_5\text{OH}$ , 99.7%, Guangfu) were all used as received.

The single crystals of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  were synthesized by a solvent volatilization method. For  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$ , 1.1518 g (10 mmol) of  $\text{C}_5\text{H}_{13}\text{N}_3$  were dissolved in 3 mL of ethanol, then 2 mL of hydrobromic acid (40%) were dropped slowly into it. Again, 1.434 g (5 mmol) of  $\text{MnBr}_2 \cdot 4\text{H}_2\text{O}$  were added into the solution, followed by placing the solution on the magnetic stirrer and stirring it until a clear solution was formed; then the solution was slowly evaporated at room temperature and the single crystals could be obtained after about one week. The obtained crystals were washed repeatedly three times with  $\text{C}_2\text{H}_5\text{OH}$ , and then filtered with a Büchner funnel. Finally, the crystals were dried at 50 °C in an oven for 24 hours. For  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ , 0.70 g (5 mmol) of  $\text{CH}_6\text{N}_3\text{Br}$  and 0.717 g (2.5 mmol) of  $\text{MnBr}_2 \cdot 4\text{H}_2\text{O}$  were thoroughly dissolved in 5 mL of acetonitrile. The solution was then slowly evaporated at room temperature and the single crystals of  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  can be obtained after about one week. The obtained crystals were washed repeatedly three times with  $\text{CH}_3\text{CN}$ , and then filtered by using the Büchner funnel. Finally, the crystals were dried at 50 °C in an oven for 24 hours.

### 2.2 Characterization

The single-crystal X-ray diffraction data of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  were collected at room temperature using the XtaLAB AFC12 X-ray four-circle single crystal diffractometer (Rigaku) equipped with a CCD-detector, a graphite monochromator and a Mo K $\alpha$  radiation source. The powder X-ray diffraction data of  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  and  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  were collected at room temperature with an X-ray diffractometer (Cu-K $\alpha$  radiation). The photoluminescence (PL) spectra, photoluminescence excitation (PLEX) spectra, photoluminescence emission (PLEM) spectra, fluorescence decay curve and PLQYs were measured using a FLS-920 fluorescence spectrometer (Edinburgh Instruments Ltd. UK). Temperature-dependent emission spectra were measured on the same spectrophotometer installed with a heating apparatus as the heating source. Thermogravimetric analysis (TGA) was performed on a SETARAM 131 LABSYS device under an argon stream at a heating rate of 10 °C min<sup>−1</sup> from RT to 800 °C. The emission spectra, correlated color temperature (CCT), luminous efficacy, and CIE coordinates of the LED devices were measured using an integrating sphere spectroradiometer system (ATA-100, Everfine).

### 2.3 Computational methods

The electronic band structure and density of states (DOS) were calculated by CASTEP based on plane-wave pseudopotential density functional theory (DFT).<sup>44</sup> Perdew–Burke–Ernzerhof (PBE) functionals in the generalized gradient approximation (GGA) form were used for electronic structure calculations.<sup>45</sup> The optimized norm-conserving pseudopotential in Kleinman–Bylander allows us to use a small plane basis set without compromising the required accuracy of the calculation. A kinetic energy cut off value of 900 eV and a Monkhorst–Pack *k*-point mesh spanning less than 0.03 Å<sup>−1</sup> in the Brillouin zone were chosen. The Broyden–Fletcher–Goldfarb–Shanno (BFGS) minimization scheme was employed and the convergence criteria for the structure optimization were set to  $5.0 \times 10^{-5}$  eV

per atom, 0.1 eV per Å, 0.2 GPa and  $5.0 \times 10^{-3}$  GPa which is energy, maximum force, maximum stress and maximum displacement, respectively.

### 3. Results and discussion

#### 3.1 Synthesis and structure evolution

The  $\text{Mn}^{2+}$ -based bromides of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  were synthesized by a solvent volatilization method, and their single crystal data are collected at room temperature (RT). The orientation matrix and cell parameters of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  were defined and refined for the set of 5077 and 23264 reflections, respectively. The unit cell corresponds to a monoclinic symmetry in both cases. Space groups  $C2/c$  and  $P2_1/c$  were determined by utilizing the statistical analysis of the intensities of all the reflections. The absorption correction using spherical harmonics was applied using the ABSPAK program. The crystal structure was solved by using package SHELXS and refined *via* the anisotropic approach for non-hydrogen atoms using the SHELXL program.<sup>46</sup> All the hydrogen atoms of the ligands were positioned geometrically as riding on their parent atoms with  $d(\text{C}-\text{H}) = 0.97$  Å for the C–H bonds and  $d(\text{N}-\text{H}) = 0.86$  Å for all other N–H bonds and  $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C}, \text{N})$ . The main crystal data are shown in Table 1. The crystallographic data are deposited in the Cambridge Crystallographic Data Centre (CCDC # 2094640–2094641). The coordinates of atoms are in Table S1 (ESI<sup>†</sup>), and the main bond lengths are shown in Table S2 (ESI<sup>†</sup>). The asymmetric part of the  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  unit cell includes one organic cation of  $[\text{C}_5\text{H}_{14}\text{N}_3]^{2+}$ , one half of  $\text{Mn}^{2+}$  and two  $\text{Br}^-$  ions. The  $\text{Mn}^{2+}$  ion is coordinated with four  $\text{Br}^-$  ions to form the  $[\text{MnBr}_4]^{2-}$  tetrahedron (Fig. 1a). The tetrahedra are isolated from each other to form a 0D structure (Fig. 1b). There are two  $\text{N}-\text{H} \cdots \text{Br}$  hydrogen bonds (Table S3, ESI<sup>†</sup>), which join the organic cations  $[\text{C}_5\text{H}_{14}\text{N}_3]^{2+}$  with  $[\text{MnBr}_4]^{2-}$  tetrahedra and form a three-dimensional (3D) net. The asymmetric part of the  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  unit cell contains six organic cations of  $[\text{CH}_6\text{N}_3]^{2+}$ , three  $\text{Mn}^{2+}$  and twelve  $\text{Br}^-$  ions. All  $\text{Mn}^{2+}$  ions are coordinated by six  $\text{Br}^-$  ions to form  $\text{MnBr}_6$  octahedra (Fig. 1d). These octahedra are linked with each other by sharing faces to form an isolated 0D block (Fig. 1c). There are 33

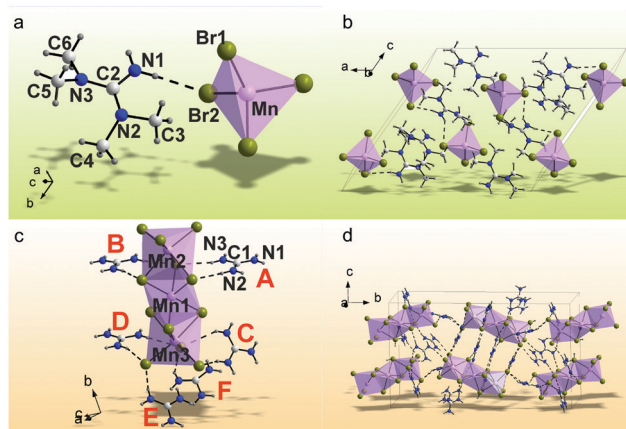


Fig. 1 Crystal asymmetric structure units of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  (a) and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (c). The atoms in the asymmetric part of the unit cell  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  (b) and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (d) are labeled, the hydrogen bonds in which are presented as dashed lines. The independent  $[\text{CH}_6\text{N}_3]^{2+}$  cations in the Figure (c) are marked by bold labels A–E.

$\text{N}-\text{H} \cdots \text{Br}$  hydrogen bonds (Table S3, ESI<sup>†</sup>) between the organic cations  $[\text{CH}_6\text{N}_3]^{2+}$  and  $[\text{Mn}_3\text{Br}_{12}]^{6-}$  polyhedra, all of which stack together to form a 3D net. Fig. S1 (ESI<sup>†</sup>) shows the PXRD patterns of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ , indicating that the obtained powders are pure phases and are consistent with their single crystal phases, respectively. In addition, the organic functional groups were characterized by FTIR spectra in Fig. S2 (ESI<sup>†</sup>).<sup>47,48</sup> It is observed that  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  both exhibit the absorption peaks at  $\sim 3300$   $\text{cm}^{-1}$ ,  $\sim 1650$   $\text{cm}^{-1}$  and  $\sim 1000$   $\text{cm}^{-1}$ , which are ascribed to the stretching vibration, blending vibration of N–H and the C–N stretching vibration, respectively. Compared with  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ ,  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  possess additional absorption peaks at  $\sim 2950$   $\text{cm}^{-1}$ ,  $\sim 2850$   $\text{cm}^{-1}$  and  $\sim 1370$   $\text{cm}^{-1}$ , which are assigned to the  $-\text{CH}_3$  asymmetric, symmetric stretching vibrations and deformation vibrations, respectively.

#### 3.2 Photoluminescence tuning and mechanism

The transition metal ion  $\text{Mn}^{2+}$  has a  $3d^5$  electronic configuration. Since the 3d orbital electrons of  $\text{Mn}^{2+}$  are exposed in the outer layer, the wavelength position of the emission band of  $\text{Mn}^{2+}$  is strongly affected by the crystal field environment. In view of this, the coordination units of  $\text{Mn}^{2+}$  can be modified by employing different organic ligands toward tunable emission in 0D bromides. The photoluminescence (PL) and photoluminescence excitation (PLE) spectra of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  are shown in Fig. 2a and b. They exhibit a green emission at 528 nm and a red emission at 627 nm under excitation at 365 and 375 nm, respectively, which are originated from the d–d transition ( ${}^4\text{T}_1(\text{G}) \rightarrow {}^6\text{A}_1(\text{S})$ ) of four coordinated  $[\text{MnBr}_4]^{2-}$  units and six coordinated  $[\text{Mn}_3\text{Br}_{12}]^{6-}$  units, respectively. In particular,  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  presents absorption peaks at the blue region, corresponding to the transitions of  ${}^6\text{A}_1 \rightarrow {}^4\text{A}_1(\text{G})$ ,  ${}^4\text{E}(\text{G})$  and  ${}^6\text{A}_1 \rightarrow {}^4\text{T}_2(\text{G})$ , which enables them to be applied to white LEDs pumped by blue light. The UV-visible absorption spectra of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and

Table 1 Main crystal structure parameters of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$

| Chemical formula                          | $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$ | $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ |
|-------------------------------------------|------------------------------------------------------|------------------------------------------|
| Weight, g mol <sup>−1</sup>               | 606.96                                               | 494.76                                   |
| Temperature (K)                           | 293                                                  | 293                                      |
| Space group, Z                            | $C2/c$ , 4                                           | $P2_1/c$ , 12                            |
| a (Å)                                     | 19.215 (3)                                           | 9.0171 (3)                               |
| b (Å)                                     | 9.2604 (7)                                           | 27.9628 (10)                             |
| c (Å)                                     | 15.366 (2)                                           | 16.1020 (5)                              |
| $\beta$ (°)                               | 125.51 (2)                                           | 93.016 (3)                               |
| V (Å <sup>3</sup> )                       | 2225.6 (6)                                           | 4054.4 (2)                               |
| $\rho_{\text{calc}}$ , g cm <sup>−3</sup> | 1.811                                                | 2.432                                    |
| $R_{\text{int}}$                          | 0.0496                                               | 0.0546                                   |
| $2\theta_{\text{max}}$ , °                | 58.34                                                | 59.18                                    |
| $R1$ [ $F_o > 4\sigma(F_o)$ ]             | 0.0697                                               | 0.0508                                   |
| wR2                                       | 0.1913                                               | 0.1363                                   |
| Goof                                      | 0.828                                                | 0.898                                    |

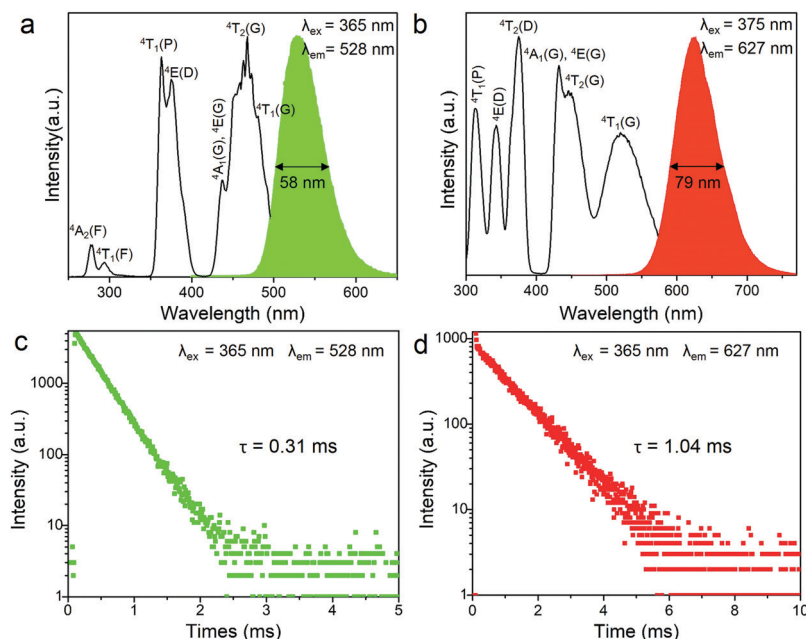


Fig. 2 The photoluminescence (PL) and photoluminescence excitation (PLE) spectra of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  (a) and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (b) at room temperature (RT). Photoluminescence decay curves of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  (c) and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (d) at RT under excitation at 365 nm, emission at 528/627 nm.

$(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  are shown in Fig. S3 (ESI†). The decay curves monitored at  $\lambda_{\text{em}} = 528 \text{ nm}$  and  $\lambda_{\text{em}} = 627 \text{ nm}$  were collected under 365 nm excitation, as shown in Fig. 2c and d. They can be fitted by utilizing the following decay equation:<sup>49,50</sup>

$$I(t) = I_0 + A \exp(-t/\tau) \quad (1)$$

where  $I(t)$  and  $I_0$  are the luminescence intensity at time  $t$  and  $t \gg \tau$ , respectively.  $A$  is a constant, and  $\tau$  is the decay time, which is an exponential component. The lifetimes of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  are determined to be 0.31 and 1.04 ms, respectively, which possess relatively short lifetimes. Among them, the lifetime value of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  is consistent with that reported in the literature,<sup>14,15</sup> which indicates that the green-light emission originates from the d-d transition ( $^4\text{T}_1(\text{G}) \rightarrow ^6\text{A}_1(\text{S})$ ) of four coordinated  $[\text{MnBr}_4]^{2-}$  units. The lifetime value of  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  has not been proven, but compared with the similar  $\text{A}_2\text{BX}_4$  type  $\text{Mn}^{2+}$ -based chlorides,<sup>42,43</sup> its lifetime value is smaller, which is in line with the law of the influence of halogen ions on the lifetime in green-emitting  $\text{Mn}^{2+}$ -based halides.<sup>15</sup> Accordingly, the red emission peaked at 627 nm is attributed to the d-d transition ( $^4\text{T}_1(\text{G}) \rightarrow ^6\text{A}_1(\text{S})$ ) of six coordinated  $[\text{Mn}_3\text{Br}_{12}]^{6-}$  units.

In addition,  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  both exhibit the broadband emissions, with a relatively large FWHM of 58 nm and 79 nm at RT, respectively, which is conducive to the application of such materials in solid-state lighting. Fig. 3a and b show the temperature-dependent PL spectra in the range of 80–300 K. The emission peak position of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  hardly changed, while the emission peak position of  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  showed a blue-shift from 655 nm to 627 nm, which is mainly ascribed to the following two reasons. On the

one hand,  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  has a high crystal field strength, and the thermally induced host lattice expansion has a significant effect on the crystal field strength, resulting in the value of that reduce significantly.

On the other hand, the crystal expansion reduced the spin-spin coupling energy ( $E_{\text{sc}}$ ) of locally adjacent  $\text{Mn}^{2+}$  ions in the crystal such as Frenkel exciton coupling in molecular aggregates.

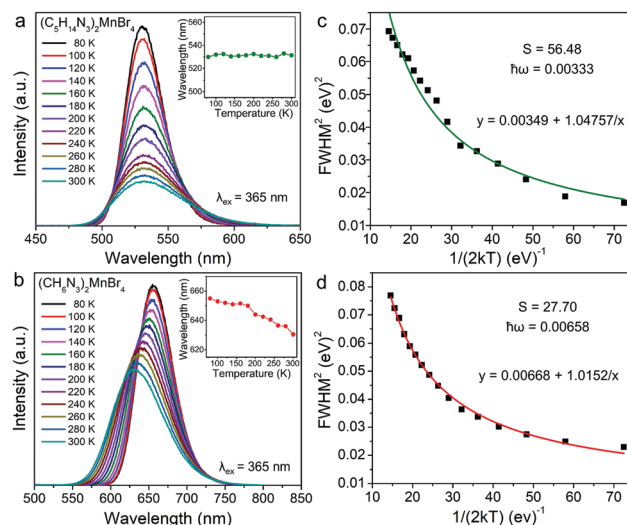
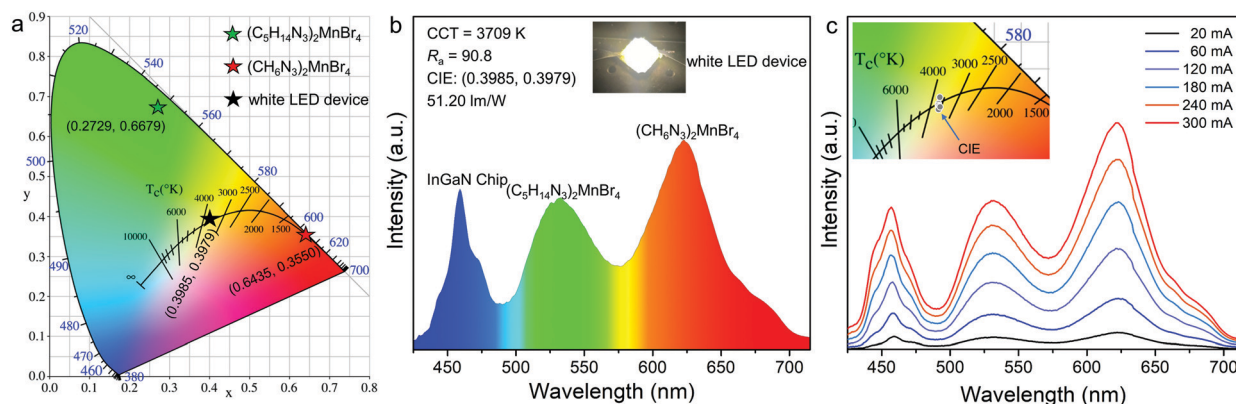


Fig. 3 Temperature-dependent PL spectra of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  (a) and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (b) under 365 nm excitation in the range from 80 to 300 K. Inset: the temperature-dependent emission peak. The FWHM fitting curve of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  (c) and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (d) as a function of temperature via the eqn (4) to obtain the Huang–Phys factor  $S$  and maximum phonon energy  $\hbar\omega$ .





**Fig. 6** (a) CIE chromaticity diagram of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$ ,  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ , and the fabricated white LED device. (b) Emission spectrum and photograph of the white LED device fabricated with the green emitting  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and the red emitting  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  on a blue LED chip (460 nm) under a current of 20 mA. (c) Emission spectra of the white LED device under the driving currents ranges from 20 to 300 mA, and the inset showing the CIE chromaticity coordinates changes.

defined as<sup>57,58</sup>

$$D = \frac{1}{n} \sum_{i=1}^n \frac{|l_i - l_{av}|}{l_{av}} \quad (5)$$

where  $l_i$  is the distance between the central atom Mn and the coordinated halogen atom, and  $l_{av}$  is the average bond length. For  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$ , the distortion index of  $[\text{MnBr}_4]^{2-}$  is  $2.16 \times 10^{-3}$ , while for  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$ , the distortion index of three  $\text{MnBr}_6$  octahedrons in  $[\text{Mn}_3\text{Br}_{12}]^{6-}$  are  $7.97 \times 10^{-3}$ ,  $3.55 \times 10^{-2}$  and  $3.73 \times 10^{-2}$  respectively, with an average value of  $2.69 \times 10^{-2}$ . So the distortion index of  $[\text{Mn}_3\text{Br}_{12}]^{6-}$  is much higher than that of  $[\text{MnBr}_4]^{2-}$ . Therefore, compared with  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$ , the emission peak of  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  have a large redshift, which is coincident with the observed experimental phenomenon. As for the  $\text{MnX}_6$  units, they usually show orange emission due to the large polyhedral distortion. If these octahedrons combine together by sharing planes with each other, the orange emission shifts to the red emission, which means the increase in distortion index and crystal field strength. As shown in Fig. 4b, the coordination units of  $\text{Mn}^{2+}$  can be modified by employing different organic cations toward tunable emission in 0D bromides. The  $\text{Mn}^{2+}$  in  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  is located in the tetrahedral weak field, so it exhibits a green light emission. While the  $\text{Mn}^{2+}$  in  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  is located in the octahedral strong field and these  $\text{MnBr}_6$  octahedral units form a trimetric  $[\text{Mn}_3\text{Br}_{12}]^{6-}$  unit by sharing planes with each other, so it exhibits a red light emission.

In addition, the electronic energy band structures of 0D bromides with different coordination units of  $\text{Mn}^{2+}$  are calculated based on the density functional theory (DFT) approach. As illustrated in Fig. 5a and b, the calculated energy gaps for  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  are estimated to be around 3.87 eV at the G point of the Brillouin zone and 2.96 eV at the D point of the Brillouin zone, respectively. The total density states (TDOS) and orbital-projected partial density of states (PDOS) diagrams for  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (Fig. 5c and d) indicate that the electronic states in the valence band maximum (VBM) are mainly attributed to Br-p and Mn-d orbitals, while those in

the conduction band minimum (CBM) are said to principally originate from organic groups.

### 3.3 Stability and application for LEDs

The 0D bromides of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  can be effectively excited by a 450 nm blue light and exhibit relatively high photoluminescence quantum yields (PLQYs) of 86.83% and 61.91%, which enables the corresponding white light LED devices encapsulated by them to achieve a high luminous efficacy in the practical application of solid-state lighting. Meanwhile, their chemical stabilities and temperature quenching (TQ) behaviors were evaluated. The thermogravimetric (TG) results (Fig. S4, ESI<sup>†</sup>) show that  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  are chemically stable up to 281 °C and 289 °C, respectively. The temperature dependent PL spectra (Fig. S5, ESI<sup>†</sup>) indicate that their thermal quenching behaviors are obvious, especially after reaching 100 °C. To further evaluate their practical application prospects in solid-state lighting, the white LED device was fabricated by utilizing the green-emitting  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and red-emitting  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  (Fig. 6a and b). The results present a correlated color temperature of 3709 K, along with CIE chromaticity coordinates of (0.3985, 0.3979), which means that there is no need to add commercial phosphors containing rare earth as a strategic resource to produce white light emission. The white LED device exhibits a luminous efficacy (LE) of  $51.20 \text{ lm W}^{-1}$  and a high color rendering index ( $R_a$ ) of 90.8, indicating the potential of the as-synthesized  $\text{Mn}^{2+}$ -based 0D bromides in solid-state lighting. Moreover, the emission spectra and enlarged view of CIE chromaticity coordinates present no remarkable change under different driving currents from 20 to 300 mA (Fig. 6c), revealing a good electroluminescence stability of the fabricated white LEDs. It is found that the 0D bromides of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  are suitable to act as the high-performance green and red phosphors for white LED applications.

## 4. Conclusions

In summary, the 0D bromides of  $(\text{C}_5\text{H}_{14}\text{N}_3)_2\text{MnBr}_4$  and  $(\text{CH}_6\text{N}_3)_2\text{MnBr}_4$  with variable coordination units of  $\text{Mn}^{2+}$  were

designed and synthesized by a facile method of solvent evaporation. They exhibit a green emission at 528 nm and a red emission at 627 nm with a relatively large FWHM of 59 nm and 79 nm under excitation under UV/blue light, which are attributed to the d-d transition ( ${}^4T_1(G) \rightarrow {}^6A_1(S)$ ) of four coordinated  $[MnBr_4]^{2-}$  units and six coordinated  $[Mn_3Br_{12}]^{6-}$  units, respectively. According to the temperature-dependent PL spectra from 80 K to 300 K and Tanabe-Sugano (TS) energy diagram, the 0D bromides of  $(C_5H_{14}N_3)_2MnBr_4$  and  $(CH_6N_3)_2MnBr_4$  show relatively large Huang-Rhys factor  $S$  ( $S = 56.48$ ;  $S = 27.70$ ), and the distortion index of  $[Mn_3Br_{12}]^{6-}$  ( $D = 2.69 \times 10^{-2}$ ) is much higher than that of  $[MnBr_4]^{2-}$  ( $D = 2.16 \times 10^{-3}$ ), resulting in the emission position of  $(CH_6N_3)_2MnBr_4$  having a large redshift compared to that of  $(C_5H_{14}N_3)_2MnBr_4$ . The cases emphasize the influence of organic ligands on the intrinsic emissions of  $Mn^{2+}$  ions, and it is found that the 0D bromides of  $(C_5H_{14}N_3)_2MnBr_4$  and  $(CH_6N_3)_2MnBr_4$  are suitable to act as the high-performance green and red phosphors for white LED applications. The fabricated white LED device shows an excellent  $R_a$  of 90.8 at a correlated color temperature of 3709 K, along with CIE chromaticity coordinates of (0.3985, 0.3979). This work aims at clarifying the relationship between the coordination units of  $Mn^{2+}$  and emission tuning, and in particular proposes a new way to explore phosphors excited by blue light for white LEDs.

## Author contributions

G. Z. and M. X. Z. conceived the project, wrote and revised the paper, and was primarily responsible for the experiment. J. D. synthesized the materials, performed the experimental characterization, and wrote a part of the paper. X. J. and J. Z. performed the DFT calculations. M. M performed the structure analysis. Q. R., J. Z., and S. L. contributed the luminescence mechanism analysis. All authors contributed to the general discussion.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The present work was supported by the Natural Science Foundation of China (21871167), the 1331 Project of Shanxi Province and the Postgraduate Innovation Project of Shanxi Normal University (2019XBY018), the Beijing Natural Science Foundation (No. 2214068) and funded by RFBR according to the research project no. 19-52-80003.

## Notes and references

- 1 L. N. Quan, B. P. Rand, R. H. Friend, S. G. Mhaisalkar, T. W. Lee and E. H. Sargent, *Chem. Rev.*, 2019, **119**, 7444–7477.
- 2 Y. H. Dong, Y. S. Zou, J. Z. Song, X. F. Song and H. B. Zeng, *J. Mater. Chem. C*, 2017, **5**, 11369–11394.
- 3 Y. Zhang, W. Q. Liao, D. W. Fu, H. Y. Ye, Z. N. Chen and R. G. Xiong, *J. Am. Chem. Soc.*, 2015, **137**, 4928–4931.
- 4 J. Y. Kim, J.-W. Lee, H. S. Jung, H. Shin and N.-G. Park, *Chem. Rev.*, 2020, **120**, 7867–7918.
- 5 Q. Q. He, C. K. Zhou, L. J. Xu, S. Lee, X. S. Lin, J. Neu, M. Worku, M. Chaaban and B. W. Ma, *ACS Mater. Lett.*, 2020, **2**, 633–638.
- 6 P. P. Du, L. Gao and J. Tang, *Front. Optoelectron.*, 2020, **13**, 235–245.
- 7 G. J. Zhou, B. B. Su, J. L. Huang, Q. Y. Zhang and Z. G. Xia, *Mater. Sci. Eng., R*, 2020, **141**, 100548.
- 8 P. F. Fu, S. L. Hu, J. Tang and Z. W. Xiao, *Front. Optoelectron.*, 2021, **14**, 252–259.
- 9 C. K. Zhou, H. Lin, S. Lee, M. Chaaban and B. W. Ma, *Mater. Res. Lett.*, 2018, **6**, 552–569.
- 10 L. J. Xu, S. Lee, X. Lin, L. Ledbetter, M. Worku, H. Lin, C. K. Zhou, H. Liu, A. Plaviak and B. W. Ma, *Angew. Chem., Int. Ed.*, 2020, **59**, 14120–14123.
- 11 M. Z. Li and Z. G. Xia, *Chem. Soc. Rev.*, 2021, **50**, 2626–2662.
- 12 C. K. Zhou, L. J. Xu, S. Lee, H. R. Lin and B. W. Ma, *Adv. Opt. Mater.*, 2020, **9**, 2001766.
- 13 L. L. Mao, P. J. Guo, S. X. Wang, A. K. Cheetham and R. Seshadri, *J. Am. Chem. Soc.*, 2020, **142**, 13582–13589.
- 14 G. J. Zhou, Z. Y. Liu, J. L. Huang, M. S. Molokeev, Z. W. Xiao, C. G. Ma and Z. G. Xia, *J. Phys. Chem. Lett.*, 2020, **11**, 5956–5962.
- 15 V. Morad, I. Cherniukh, L. Pötschacher, Y. Shynkarenko, S. Yakunin and M. V. Kovalenko, *Chem. Mater.*, 2019, **31**, 10161–10169.
- 16 P. F. Fu, Y. L. Sun, Z. G. Xia and Z. W. Xiao, *J. Phys. Chem. Lett.*, 2021, **12**, 7394–7399.
- 17 Z. W. Xiao, Z. N. Song and Y. F. Yan, *Adv. Mater.*, 2019, **31**, 1803792.
- 18 K. Dave, M. H. Fang, Z. Bao, H. T. Fu and R. S. Liu, *Chem. – Asian J.*, 2020, **15**, 242–252.
- 19 Q. Q. Fan, G. V. Biesold-McGee, J. Z. Ma, Q. N. Xu, S. Pan, J. Peng and Z. Q. Lin, *Angew. Chem., Int. Ed.*, 2020, **59**, 1030–1046.
- 20 G. Q. Ji, C. Z. Han, S. L. Hu, P. F. Fu, X. Chen, J. G. Guo, J. Tang and Z. W. Xiao, *J. Am. Chem. Soc.*, 2021, **143**, 10275–10281.
- 21 B. B. Su, G. J. Zhou, J. L. Huang, E. H. Song, A. Nag and Z. G. Xia, *Laser Photonics Rev.*, 2020, **15**, 2000334.
- 22 Q. Zhou, L. Dolgov, A. M. Srivastava, L. Zhou, Z. L. Wang, J. Shi, M. D. Dramićanin, M. G. Brik and M. M. Wu, *J. Mater. Chem. C*, 2018, **6**, 2652–2671.
- 23 Q. K. Ba, A. Jana, L. H. Wang and K. S. Kim, *Adv. Funct. Mater.*, 2019, **29**, 1904768.
- 24 H. Y. Ye, Q. Zhou, X. Niu, W. Q. Liao, D. W. Fu, Y. Zhang, Y. M. You, J. Wang, Z. N. Chen and R. G. Xiong, *J. Am. Chem. Soc.*, 2015, **137**, 13148–13154.
- 25 A. K. Guria, S. K. Dutta, S. Das Adhikari and N. Pradhan, *ACS Energy Lett.*, 2017, **2**, 1014–1021.
- 26 G. C. Hu, B. Xu, A. F. Wang, Y. Guo, J. J. Wu, F. Muhammad, W. Meng, C. Y. Wang, S. Q. Sui, Y. Liu, Y. C. Li, Y. Zhang,

- Y. G. Zhou and Z. T. Deng, *Adv. Funct. Mater.*, 2021, **31**, 2011191.
- 27 T. M. Jiang, W. B. Ma, H. Zhang, Y. Tian, G. Lin, W. G. Xiao, X. Yu, J. B. Qiu, X. H. Xu, Y. Yang and D. X. Ju, *Adv. Funct. Mater.*, 2021, **31**, 2009973.
- 28 F. Locardi, M. Cirignano, D. Baranov, Z. Dang, M. Prato, F. Drago, M. Ferretti, V. Pinchetti, M. Fanciulli, S. Brovelli, L. De Trizio and L. Manna, *J. Am. Chem. Soc.*, 2018, **140**, 12989–12995.
- 29 W. Y. Liu, Q. L. Lin, H. B. Li, K. F. Wu, I. Robel, J. M. Pietryga and V. I. Klimov, *J. Am. Chem. Soc.*, 2016, **138**, 14954–14961.
- 30 J. D. Majher, M. B. Gray, T. A. Strom and P. M. Woodward, *Chem. Mater.*, 2019, **31**, 1738–1744.
- 31 A. Biswas, R. Bakthavatsalam and J. Kundu, *Chem. Mater.*, 2017, **29**, 7816–7825.
- 32 C. K. Zhou, Y. Tian, O. Khabou, M. Worku, Y. Zhou, J. Hurley, H. R. Lin and B. W. Ma, *ACS Appl. Mater. Interfaces*, 2017, **9**, 40446–40451.
- 33 S. K. Dutta, A. Dutta, S. Das Adhikari and N. Pradhan, *ACS Energy Lett.*, 2018, **4**, 343–351.
- 34 G. J. Zhou, X. X. Jiang, M. Molokeev, Z. S. Lin, J. Zhao, J. Wang and Z. G. Xia, *Chem. Mater.*, 2019, **31**, 5788–5795.
- 35 L. K. Gong, Q. Q. Hu, F. Q. Huang, Z. Z. Zhang, N. N. Shen, B. Hu, Y. Song, Z. P. Wang, K. Z. Du and X. Y. Huang, *Chem. Commun.*, 2019, **55**, 7303–7306.
- 36 C. L. Jiang, N. Zhong, C. H. Luo, H. C. Lin, Y. Y. Zhang, H. Peng and C. G. Duan, *Chem. Commun.*, 2017, **53**, 5954–5957.
- 37 S. Zhang, Y. F. Zhao, J. D. Zhou, H. Ming, C. H. Wang, X. P. Jing, S. Ye and Q. Y. Zhang, *Chem. Eng. J.*, 2021, **421**, 129886.
- 38 M. Z. Li, J. Zhou, M. S. Molokeev, X. X. Jiang, Z. S. Lin, J. Zhao and Z. G. Xia, *Inorg. Chem.*, 2019, **58**, 13464–13470.
- 39 G. J. Zhou, Z. Y. Liu, M. S. Molokeev, Z. W. Xiao, Z. G. Xia and X.-M. Zhang, *J. Mater. Chem. C*, 2021, **9**, 2047–2053.
- 40 M. Zhao, H. X. Liao, M. S. Molokeev, Y. Y. Zhou, Q. Y. Zhang, Q. L. Liu and Z. G. Xia, *Light Sci. Appl.*, 2019, **8**, 38.
- 41 L. Y. Lian, P. Zhang, G. Liang, S. Wang, X. Wang, Y. Wang, X. W. Zhang, J. B. Gao, D. L. Zhang, L. Gao, H. S. Song, R. Chen, X. Z. Lan, W. X. Liang, G. D. Niu, J. Tang and J. B. Zhang, *ACS Appl. Mater. Interfaces*, 2021, **13**, 22749–22756.
- 42 S. Y. Wang, X. X. Han, T. T. Kou, Y. Y. Zhou, Y. Liang, Z. X. Wu, J. L. Huang, T. Chang, C. Y. Peng, Q. L. Wei and B. S. Zou, *J. Mater. Chem. C*, 2021, **9**, 4895–4902.
- 43 A. Sen, D. Swain, T. N. Guru Row and A. Sundaresan, *J. Mater. Chem. C*, 2019, **7**, 4838–4845.
- 44 S. J. Clark, M. D. Segall, C. J. Pickard, P. J. Hasnip, M. I. J. Probert, K. Refson and M. C. Payne, *Z. Kristallogr.*, 2005, **220**, 567–570.
- 45 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 46 G. Sheldrick, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 2008, **64**, 112–122.
- 47 Y. F. Zhao, R. R. Yang, W. Wan, X. P. Jing, T. Wen and S. Ye, *Chem. Eng. J.*, 2020, **389**, 124453.
- 48 H. Y. Huang, R. T. Yang, D. Chinn and C. L. Munson, *Ind. Eng. Chem. Res.*, 2003, **42**, 2427–2433.
- 49 R. Pang, C. Li, L. Shi and Q. Su, *J. Phys. Chem. Solids*, 2009, **70**, 303–306.
- 50 S. P. Lee, C. H. Huang, T. S. Chan and T. M. Chen, *ACS Appl. Mater. Interfaces*, 2014, **6**, 7260–7267.
- 51 X. F. Zhou, W. Y. Geng, J. Y. Li, Y. C. Wang, J. J. Ding and Y. Y. Wang, *Adv. Opt. Mater.*, 2020, **8**, 1902003.
- 52 H. Siddique, Z. L. Xu, X. D. Li, S. Saeed, W. T. Liang, X. Q. Wang, C. Gao, R. C. Dai, Z. P. Wang and Z. M. Zhang, *J. Phys. Chem. Lett.*, 2020, **11**, 9572–9578.
- 53 J. Ruiz-Fuertes, S. López-Moreno, J. López-Solano, D. Errandonea, A. Segura, R. Lacomba-Perales, A. Muñoz, S. Radescu, P. Rodríguez-Hernández, M. Gospodinov, L. L. Nagornaya and C. Y. Tu, *Phys. Rev. B: Condens. Matter Phys.*, 2012, **86**, 125202.
- 54 Z. H. Leng, R. F. Li, L. P. Li, D. K. Xue, D. Zhang, G. S. Li, X. Y. Chen and Y. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 33322–33334.
- 55 K. A. Denault, J. Brgoch, M. W. Gaultois, A. Mikhailovsky, R. Petry, H. Winkler, S. P. DenBaars and R. Seshadri, *Chem. Mater.*, 2014, **26**, 2275–2282.
- 56 Z. Q. Ming, J. W. Qiao, M. S. Molokeev, J. Zhao, H. C. Swart and Z. G. Xia, *Inorg. Chem.*, 2020, **59**, 1405–1413.
- 57 L. Zhou, J. F. Liao, Z. G. Huang, J. H. Wei, X. D. Wang, H. Y. Chen and D. B. Kuang, *Angew. Chem., Int. Ed.*, 2019, **58**, 15435–15440.
- 58 W. Baur, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1974, **30**, 1195–1215.