



Cite this: *J. Mater. Chem. A*, 2024, **12**, 1840  
1840

## Covalency-aided electrochemical $\text{CO}_2$ reduction to CO on sulfide-derived Cu–Sb†

Daniel Yong Yi Goh, <sup>ab</sup> Kah Meng Yam, <sup>de</sup> Lavie Rekhi, <sup>d</sup>  
Albertus Denny Handoko, <sup>c</sup> Ying Chuan Tan, <sup>c</sup> Yong Wang, <sup>a</sup>  
Joel Ming Rui Tan, <sup>af</sup> Tej Salil Choksi, <sup>\*de</sup> Yanwei Lum <sup>\*b</sup>  
and Lydia Helena Wong <sup>\*af</sup>

p-Block dopants like sulfur have been shown to break scaling relations in the electrocatalytic  $\text{CO}_2$  reduction reaction (CO<sub>2</sub>RR) by providing alternative binding sites with altered \*CO binding energy. However, most sulfide-derived catalysts reported to date tend to produce formate or hydrogen during the CO<sub>2</sub>RR by shifting the reaction pathway away from C-bound intermediates. In this work, we discovered highly selective CO production on a bimetallic Cu–Sb–S derived catalyst. The high CO selectivity is in contrast with the individual control samples of CuS<sub>x</sub> and SbS<sub>x</sub> that demonstrate a preference towards the formate product. Interestingly, different starting phases and atomic ratios of Cu–Sb–S affect the CO<sub>2</sub>RR selectivity. Post-catalysis characterization coupled with DFT calculations indicates that the key enabler towards CO formation is the substitution of Sb sites with sulfur which improves \*COOH binding relative to \*CO, breaking scaling relations and facilitating subsequent CO (g) formation. The highest CO production of  $\text{FE}_{\text{CO}} = 80.5\%$  was observed on the tetrahedrite Cu–Sb–S-derived sample at  $-1.0\text{ V RHE}$  with  $37.6\text{ mA cm}^{-2}$  geometric partial current density.

Received 10th August 2023  
Accepted 30th November 2023

DOI: 10.1039/d3ta04777f  
[rsc.li/materials-a](http://rsc.li/materials-a)

## Introduction

As part of the energy transition to renewable energy, efforts are underway to decarbonize industry. Electrocatalysis is regarded as a key solution to this issue, with ongoing research efforts in electrochemical  $\text{CO}_2$  reduction (CO<sub>2</sub>RR) to decarbonize the chemical and polymer industries. Carbon monoxide (CO) in particular is a crucial intermediate for the formation of value-added chemicals such as ethylene, methanol (*via* the hydrogenation reaction),<sup>1</sup> and synthetic diesel/kerosene (*via* the Fischer–Tropsch process).<sup>2,3</sup> Currently, CO is produced as part of syngas, made from the gasification of coal or steam reforming of methane which can then be further processed or hydrogenated to form useful chemicals. However, this introduces

fossil carbon into the carbon cycle which contributes to global warming. As part of the electrification of the energy system *via* renewables, such products should be produced *via* electrolysis or otherwise clean processes. Electrochemical  $\text{CO}_2$  reduction is an emerging solution to produce chemicals *via* the recycling of waste  $\text{CO}_2$  from hard-to-abate sectors such as steel and cement, where the main profitable products currently are CO and  $\text{HCOO}^-$ .<sup>4,5</sup> However, the state-of-the-art CO<sub>2</sub>RR catalysts for CO production, made from Ag or Au, are costly. This has spurred a search for cheaper catalysts with high CO selectivity.

Modification of the catalyst oxidation state and composition has been instrumental in achieving the desired catalytic selectivity. Oxide-derived catalysts, for example, have been shown to boost selectivity for liquid products.<sup>6</sup> However, the exact mechanism of selectivity improvements is still highly debated.<sup>7–10</sup> Other interesting examples of modification include bimetallics and catalysts with p-block dopants.<sup>11–14</sup> In particular, sulfide-derived catalysts have been widely reported to promote  $\text{HCOO}^-$ .<sup>15–17</sup> Among them, the CuS<sub>x</sub>-derived catalyst system is an interesting case because the sulfide-derived variation changes the selectivity of the Cu metal completely, from CO (and  $\text{C}_2+$ ) to  $\text{HCOO}^-$ .<sup>18–22</sup> The selectivity switch has been attributed to the presence of remnant surface sulfur, which weakens M–C binding, in turn favouring the  $\text{H}_2$  evolution reaction (HER).<sup>23–25</sup> This weakening effect seems to be observed also on other metals with p-block dopants, especially those metals with relatively strong \*CO binding.

<sup>a</sup>School of Materials Science and Engineering, Nanyang Technological University, 639798, Singapore. E-mail: [lydiawong@ntu.edu.sg](mailto:lydiawong@ntu.edu.sg)

<sup>b</sup>Institute of Materials Research and Engineering, Agency for Science, Technology and Research, 138635, Singapore. E-mail: [lunyw@nus.edu.sg](mailto:lunyw@nus.edu.sg)

<sup>c</sup>Institute of Sustainability for Chemicals, Energy and Environment, Agency for Science, Technology and Research, 138635, Singapore

<sup>d</sup>School of Chemistry, Chemical Engineering and Biotechnology, Nanyang Technological University, 637459, Singapore. E-mail: [tej.choksi@ntu.edu.sg](mailto:tej.choksi@ntu.edu.sg)

<sup>e</sup>Cambridge Centre for Advanced Research and Education in Singapore, 138602, Singapore

<sup>f</sup>Singapore-HUJ Alliance for Research and Enterprise (SHARE), Campus for Research Excellence and Technological Enterprise (CREATE), 138602, Singapore

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ta04777f>

The M-C behaviour is more convoluted when metals with weaker  $^*CO$  binding are doped with p-block elements. For example, Kim's group found that p-block dopants did not affect  $^*COOH$  and  $^*CO$  equally on the Ag surface.<sup>26</sup> In an ideal case, this unusual scaling relation violation could be exploited to enhance the  $CO_2RR$  to CO (g), by selecting dopants that would lead to stronger  $^*COOH$  while allowing weaker  $^*CO$  binding. However, controlling the p-block dopant content down to the level predicted by the theoretical calculation is challenging, due to the facile formation of stoichiometric compounds.<sup>27</sup> Unfortunately, excessive p-block element content often results in increased  $^*H$  coverage leading to prominent  $H_2$  evolution (HER).<sup>20,28</sup> Thus, high performance  $CO_2RR$  to CO demonstration on p-block doped metals with relatively weaker  $^*CO$  binding (e.g., Ag/Au/Zn) is usually performed in non-aqueous electrolytes.<sup>29,30</sup>

As a different strategy, we propose that p-block dopants can be introduced into alloys of strong and weak  $^*CO$  binding metals. Bimetallic post transition metal alloys with Cu such as Cu-In, Cu-Sn, or Cu-Sb are prime targets for this investigation, as there are many stoichiometric ternary phases that can be exploited to control the p-block element fraction. Additionally, these alloys have shown some  $CO_2RR$  intrinsic activity in aqueous electrolyte.<sup>31-33</sup> We hypothesise that the considerably different  $^*CO$  binding strength in the metal pair may resist the HER boosting seen on many single metal systems, as the p-block dopants may be stabilised only on certain favourable sites. Additionally, the doping content can be further reduced, as the leaving group and gases can be evolved under cathodic conditions.

With these considerations in mind, we selected Cu-In, Cu-Sn, and Cu-Sb as possible base alloys and sulfur (S) as the p-block dopant to construct suitable pre-catalysts for the  $CO_2RR$ . We found Cu-Sb-S to be more suitable for the  $CO_2RR$  compared to Cu-In-S and Cu-Sn-S, as the latter systems are very difficult to reduce and remain in the semiconductive sulfide form after 45 min at  $-1.0\text{ V}$  vs. the reversible hydrogen electrode (RHE; all potentials are reported against RHE). Cu-Sb-S is also a suitable system as there are multiple stoichiometric phases that can be exploited to modulate the metal and p-block element ratio (Fig. S17†), providing an effective d-band centre tuning knob.

More interestingly, we found that tetrahedrite phase (TH;  $Cu_{12}Sb_4S_{13}$ ) derived Cu-Sb outperformed the control Cu-Sb bimetallic for CO production. DFT calculations reveal that the substitution of Sb with S improves the energetics of CO formation. An optimal CO faradaic efficiency (FE) of about 80.5% on a TH-derived catalyst was obtained at an applied voltage of  $-1.0\text{ V}$  vs. the reversible hydrogen electrode (RHE; all potentials are reported against RHE unless stated).

## Results and discussion

### Material screening

We first synthesized the sulfides of Cu-In, Cu-Sn, and Cu-Sb. The preliminary  $CO_2RR$  at  $-1.0\text{ V}$  found that  $H_2$  and  $HCOO^-$  were the major products on Cu-In-S and Cu-Sn-S (Fig. S1a†),

while some CO was observed on Cu-Sb-S. Post catalysis X-ray diffraction (XRD) analysis of these compounds revealed that Cu-In-S and Cu-Sn-S were unreduced (Fig. S1b and c†), while Cu-Sb-S was reduced completely to Cu-Sb (Fig. S1d†). As both Cu-Sn-S and Cu-In-S were not reduced during the  $CO_2RR$  and generate primarily  $H_2$  and  $HCOO^-$ , we focused on Cu-Sb-S for this study.

### Characterization of Cu-Sb-S phases

Three Cu-Sb-S phases, skinnerite (SK;  $Cu_3SbS_3$ ), tetrahedrite (TH;  $Cu_{12}Sb_4S_{13}$ ), and chalcostibite (CS;  $CuSbS_2$ ) were synthesized using a one-pot heat-up synthesis method<sup>34</sup> to observe the effect of atomic composition on  $CO_2RR$  selectivity. XRD characterization confirms the identity of the respective phases (Fig. 1d-f). Field emission scanning electron microscopy (FE-SEM) showed distinct morphologies with particle size in the order of SK < TH < CS (Fig. 1a-c and S2†). In terms of length, SK showed nanoplates on the order of tens of nm, TH showed agglomerated particles of about 100 nm, while CS has the largest particle size at about 500 nm to 1  $\mu\text{m}$ .

We then analysed the elemental composition of our samples using energy-dispersive X-ray spectroscopy (EDX) and X-ray photoelectron spectroscopy (XPS) (Fig. 2, S3, and S4†). The elemental composition of our samples before reduction is close to the stoichiometric ratios, thus confirming the successful synthesis of Cu-Sb-S catalysts. XPS analysis showed two distinct species of Cu, Sb, and S each which originate in the catalyst. We attribute the two Cu species to major  $Cu^+$  and minor  $Cu^{2+}$  (due to surface oxidation), the two Sb species to major  $Sb^{3+}$  and minor  $Sb-O$  (due to surface oxidation), and the two S species to  $S^{2-}$  and adsorbed dodecanethiol (the sulfur source used for synthesis).<sup>35,36</sup>

### Electrochemical performance of Cu-Sb-S phases

We tested the synthesized Cu-Sb-S phases as catalysts by air-brushing the catalyst ink onto a GDE and testing it in a three-compartment flow cell with 1 M  $KHCO_3$  electrolyte. It was found that all Cu-Sb-S catalysts (SK, TH, and CS) produced a substantial amount of CO ( $FE_{CO} \approx 50\text{--}75\%$ ) at  $-1.0\text{ V}$  (Fig. 3). This is in contrast with the pure metal sulfide control samples of  $Cu_{1.8}S$  and  $Sb_2S_3$  (characterisation in Fig. S5†), where  $HCOO^-$  is the dominant  $CO_2RR$  product as also seen in Fig. 3, in line with the literature.<sup>18-20</sup> While we note that the CuSb alloy also produces a fair amount of CO ( $FE_{CO} \approx 35\%$ ), Cu-Sb-S catalysts significantly outperform the CuSb alloy in terms of CO production; hence, the S chalcogen may be responsible for boosting the catalytic activity.

We then proceeded to test the Cu-Sb-S catalysts for  $CO_2$  reduction in a wider potential range, from the onset potential to  $-1.2\text{ V}$ . The full electrochemical  $CO_2RR$  results are shown in Fig. 4. We found that  $FE_{CO}$  increases with more cathodic potentials and reaches a maximum of 60 to 80% at a potential of  $-1.0$  to  $-1.2\text{ V}$ . These high efficiencies contrast with  $FE_{H_2}$  and  $FE_{HCOO^-}$ , which decreased at more cathodic potentials to  $<30\%$  each at  $-1.0$  to  $-1.2\text{ V}$ . We also performed a constant current  $CO_2RR$  measurement at  $200\text{ mA cm}^{-2}$  where the catalysts retain

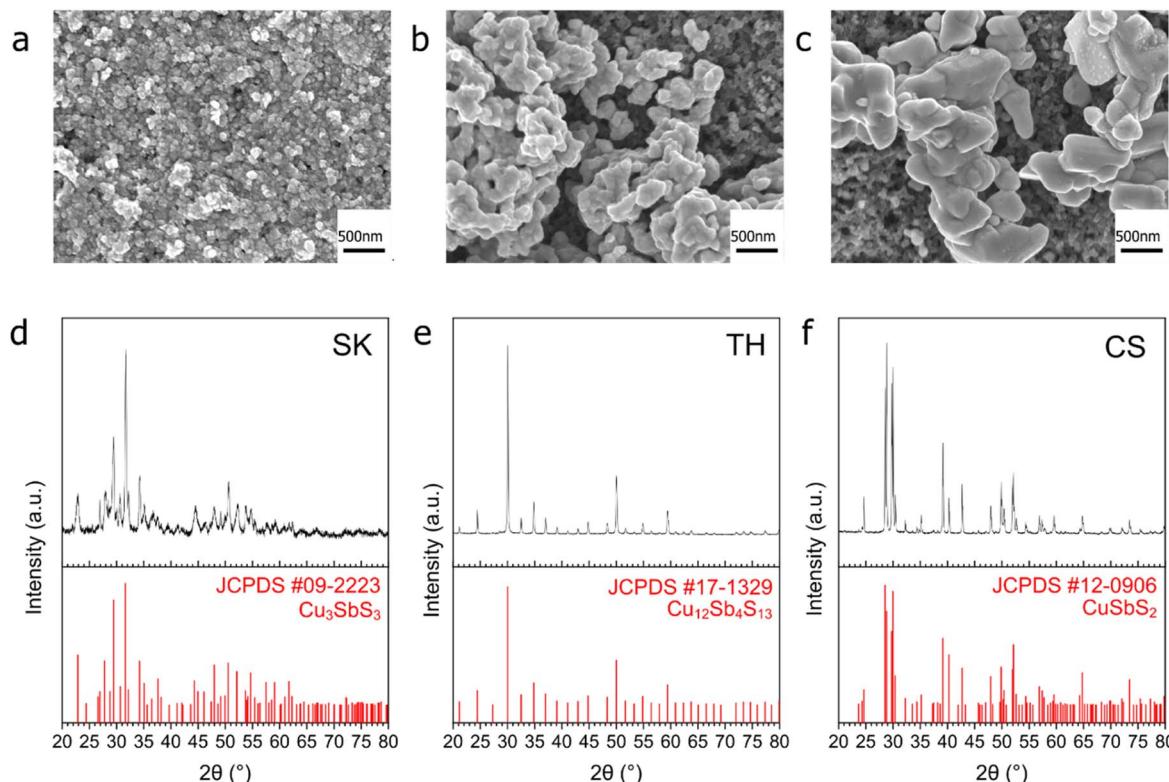


Fig. 1 XRD and SEM characterization of the samples before reduction. (a–c) SEM images of the samples SK (a), TH (b) and CS (c) sprayed on carbon paper. (d–f) XRD images of powder samples SK (d), TH (e) and CS (f).

>60% faradaic efficiency (Fig. S6†). The TH catalyst demonstrated good stability over a period of 24 h, with stable  $FE_{CO}$  in the 60–80% range (Fig. S7†). We obtain a maximum  $FE_{CO}$  of 80.5% at an applied voltage of  $-1.0$  V for the TH sample, which is comparable with the literature maximum  $FE_{CO}$  of 80–95% for Cu–Sb materials (Table S1†). We note however, that the literature reports of Cu–Sb are not pristine (deposited on Cu nanowires)<sup>37</sup> or not well-mixed (galvanic-displaced or composites)<sup>38,39</sup> and may not be accurate sulfur-free reference standards to compare our samples against. It may be that if both structural control and sulfur doping are simultaneously engineered, an even better Cu–Sb-based catalyst performance can be achieved. Our best-performing TH had a geometric partial current density of CO of about  $37.6$  mA  $cm^{-2}$  at  $-1.0$  V in a 1 M  $KHCO_3$  GDE flow cell, which is approximately seven times that of literature values of  $\sim 5$  mA  $cm^{-2}$  at the same voltage in 0.1 M  $KHCO_3$  H-type cells (Table S1†). We note that this is partially due to a difference in cell type (GDE flow cell vs. H-cell) and electrolyte concentration; thus the increase in current density due to only the catalyst would be smaller. Current densities of  $HCOO^-$  and  $H_2$  at  $-1.0$  V for the TH catalyst were  $5.7$  mA  $cm^{-2}$  and  $6.0$  mA  $cm^{-2}$  respectively.

The onset potential for CO formation is  $-0.6$  V for the Cu : Sb 3 : 1 phases (SK and TH) and  $-0.7$  V for the Cu : Sb 1 : 1 phase (CS). Electrochemically active surface area (ECSA) measurements were performed on the samples after pre-reduction (Fig. S8 and S9†), which show that SK and TH have similar total

current densities when normalized to the active surface area (by adding up the total  $J$  in Fig. 3 and dividing by the double layer capacitance). The double layer capacitance showed SK > TH > CS, which is approximately in the reverse order compared to the particle size seen in FE-SEM.

To investigate the kinetics of the reaction, Tafel slopes of the current density readings were plotted as shown in Fig. 5. The best performing TH catalyst had a lower Tafel slope of  $104$  mV  $dec^{-1}$  compared to the other two catalysts which each registered  $118$  mV  $dec^{-1}$ . According to the literature, an ideal Tafel slope of  $120$  mV  $dec^{-1}$  corresponds to an electron transfer step as the rate-determining step:  $* + CO_2 + e^- \rightarrow *CO_2^-$ .<sup>40</sup> Conversely, an ideal Tafel slope of  $60$  mV  $dec^{-1}$  corresponds to a protonation step as the rate-determining step:  $*CO_2^- + H^+ \rightarrow *COOH$ . Based on the Tafel slopes, it is possible that although the electron transfer step is the main rate-determining step, some reaction sites on the TH sample might have better kinetics with the protonation step as the rate-determining step, resulting in better CO faradaic efficiency.

#### Post-reduction characterization and remnant sulfur

CV scans were performed on the three Cu–Sb–S phases to determine the reduction potential of these samples (Fig. S10†). From the inflection point of the cathodic sweep first derivative,<sup>41,42</sup> the reduction potentials of our samples ( $-0.55$ ,  $-0.60$ , and  $-0.70$  V for SK, TH, and CS respectively, Fig. S11†) were determined to be the same or more positive than the  $CO_2RR$  to

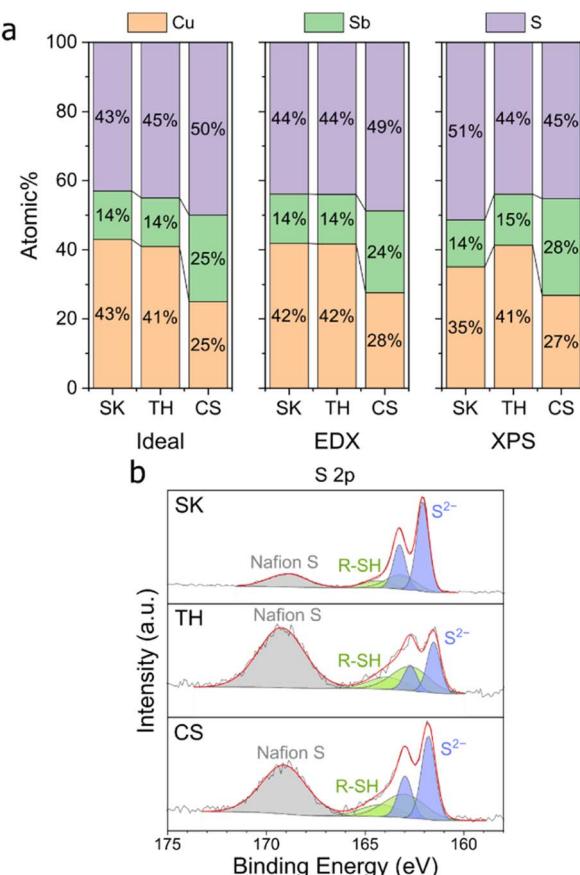


Fig. 2 EDX and XPS characterization of the samples before reduction. (a) elemental composition of samples on carbon paper. (b) XPS S 2p peaks of the samples on carbon paper.

CO onset (between  $-0.6$  and  $-0.7$  V, Fig. 4), indicating that the CO<sub>2</sub>RR to CO occurs after the reduction process of the sulfide phases.

The observation that sulfide reduction occurs before the CO<sub>2</sub>RR onset is corroborated by EDX and XPS analyses post-reduction at  $-1.0$  V (Fig. 6). A drastic decrease in the S at% was observed on all samples. Interestingly, only a small Sb at% decrease was detected. One reason for this could be because Sb forms a stable alloy with Cu, and thus it is not as easily leached compared to S. This proposition is supported by further ICP measurements of the electrolytes collected post reduction, showing that Sb had been leached at a similar rate to Cu (Table S2†), possibly due to surface reconstruction.<sup>43</sup>

Post catalysis XPS (Fig. S13†) showed that Cu<sup>2+</sup> satellite peaks appeared and the oxidized Cu<sup>2+</sup> and Sb-O peaks are noticeably enlarged, while the original Sb<sup>3+</sup> peaks at approx. 529.5 eV completely disappeared. The presence of oxidized Cu and Sb is likely due to surface reoxidation as the XPS measurements were performed *ex situ*. The presence of O in EDX and XPS most likely originated from catalyst re-oxidation post-electrolysis (Fig. S12 and S13†). We excluded O in our elemental composition analysis due to the large variation of oxygen content between samples.

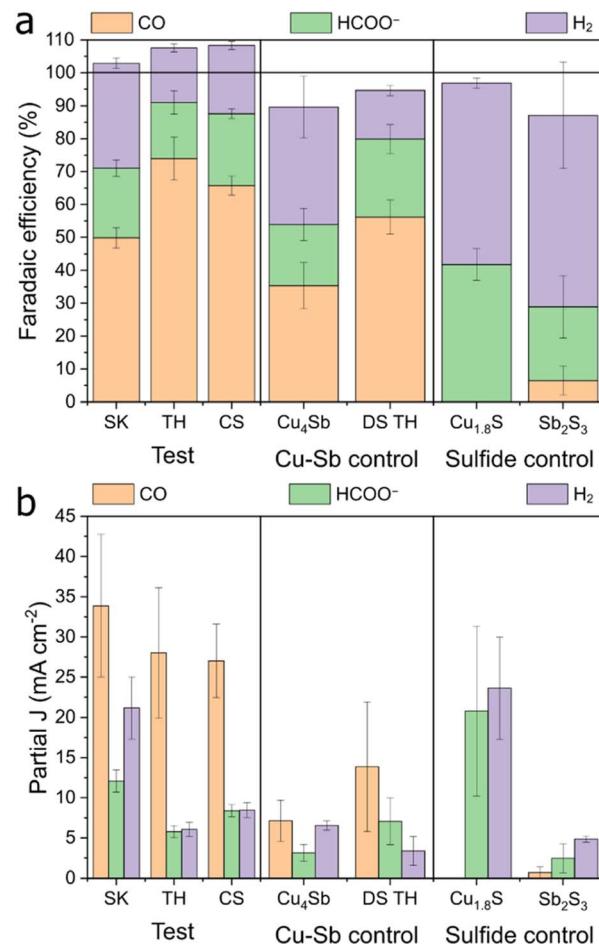


Fig. 3 Electrochemical CO<sub>2</sub>RR performance of the test vs. control (Cu-Sb or sulfide) samples at  $-1.0$  V vs. RHE. Data for (a) faradaic efficiency and (b) current density. The electrolyte used was 1 M KHCO<sub>3</sub>. For the test samples, data were collected from three individual experiments each, and the error bars represent the standard deviation.

As a result of the drastic decrease in sulfur content in the catalysts after electrochemical reduction, the active phase of our catalysts should thus be regarded as Cu-Sb alloys with remnant sulfur atoms as defects. XRD results (Fig. 6c) also showed that the dominant crystalline phase present after reduction was Cu<sub>2</sub>Sb, supporting the assignment of this phase as the active surface during the electrochemical CO<sub>2</sub>RR.

Taking the XRD data together with EDX and XPS in Fig. 6, the S and Sb amounts appear to be correlated with the crystallinity/crystallite size of the samples. The CS sample with higher Sb composition showed much smaller full-width half maximum (FWHM) peaks compared to SK and TH. TH also shows particularly broad Cu<sub>2</sub>Sb peaks, which is proposed to be linked to much higher S content. Post-reduction selected area electron diffraction (SAED, Fig. S14†) results showed very diffuse peaks that correspond to the XRD data. SEM micrographs of the catalysts after reduction showed no major changes on the micrometre scale (Fig. S15†), while TEM images of the catalysts after reduction (Fig. S16†) showed small crystallite size on the order of a few nm that corroborates the XRD findings above.

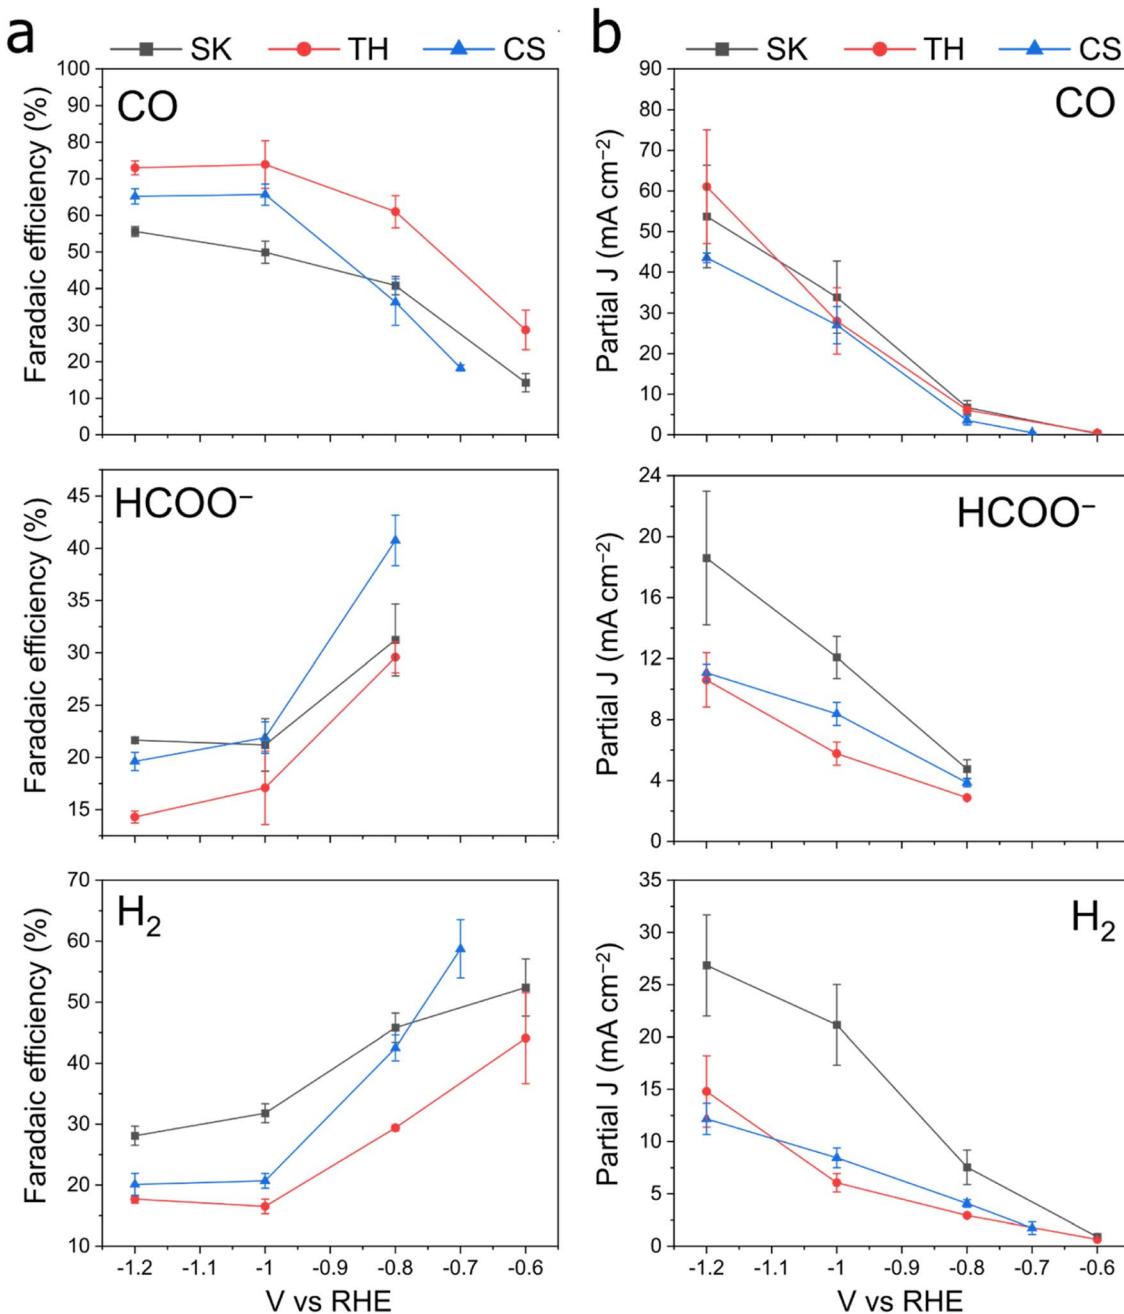


Fig. 4 Electrochemical CO<sub>2</sub>RR performance of catalysts. Data for (a) faradaic efficiency and (b) current density. The electrolyte used was 1 M KHCO<sub>3</sub>. Data were collected from three individual experiments each, and the error bars represent the standard deviation. The data are displayed for CO, HCOO<sup>-</sup> and H<sub>2</sub>.

Rietveld refinement of SK detected phase segregation of Cu<sub>2</sub>Sb and Cu (Fig. S18 and Table S3†). We posit that our SK sample contains a mixture of two phases, an S-doped Cu-Sb phase and an S-doped Cu rich phase as predicted by the phase diagram (Fig. S17†). As S-doped Cu has been shown to prefer HCOO<sup>-</sup> and H<sub>2</sub> production in the literature,<sup>18–22</sup> it is expected that the SK catalyst shows lower CO selectivity. Conversely, TH and CS catalyst compositions are closer to the Cu<sub>2</sub>Sb alloy region, which imply lower S-doped Cu content. Thus, a lower Cu amount may be advantageous to avoid Cu phase segregation

and thus suppress H<sub>2</sub> and HCOO<sup>-</sup>. This is supported by the control experiments on Cu<sub>1.8</sub>S that show a majority of H<sub>2</sub> and HCOO<sup>-</sup> products (Fig. 3a).

#### DFT calculations

Density functional theory (DFT) provides a theoretical framework for understanding the structure–activity relations of Cu-Sb-S. This information can help guide the design of experiments and catalysts for CO<sub>2</sub> reduction and improve our understanding of how these materials work. We first determine

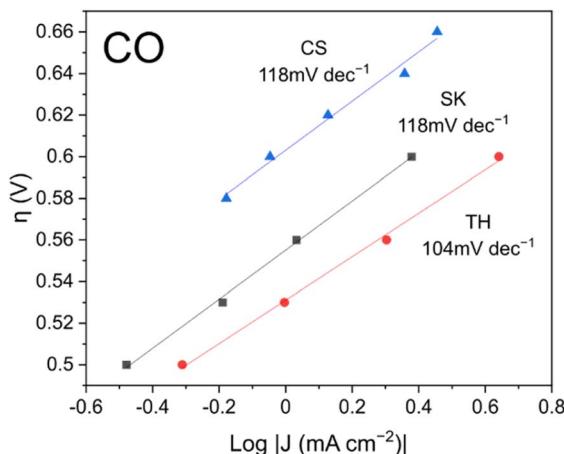


Fig. 5 CO Tafel slopes of the catalysts. Catalysts were pre-reduced for 5 min at  $-1.0$  V vs. RHE prior to the experiment.

the stability of sulfur atoms in the parent phases, *i.e.*, tetrahedrite (TH), chalcostibite (CS), and skinnerite (SK) and identify the likely contributors for improved catalytic performance.

Post-electrochemical characterisation showed significant removal of sulfur in the three parent phases. The TH phase retains the largest amount of S (7% from EDX; 15% from XPS),

which is about double that in SK (3% from EDX; 16% from XPS) and in CS (2% from EDX; 8% from XPS). We then calculated the energy penalty to form a sulfur vacancy according to eqn (S1) (ESI Section S5.2)† in primitive cells of bulk TH, CS and SK. This energy penalty reflects the likelihood of sulfur being retained in the structures. We find that the energy penalty trends as TH ( $5.46$  eV)  $>$  CS ( $5.33$  eV)  $>$  SK ( $5.23$  eV) with sulfur being most strongly bound in the TH phase. This trend is consistent with the experiments wherein the TH phase retains the highest percentage of sulfur after electrochemical tests.

Characterization studies after electrochemical testing indicated that the active phase during the  $2e^-$ -CO<sub>2</sub>RR is tetragonal Cu<sub>2</sub>Sb of space group *P4/nmm*. We calculated the Cu<sub>2</sub>Sb primitive cell lattice parameters ( $a = b = 3.98$  Å,  $c = 6.09$  Å,  $\alpha = \beta = \gamma = 90^\circ$ ) and obtained good agreement with literature values ( $a = b = 4.00$  Å,  $c = 6.10$  Å,  $\alpha = \beta = \gamma = 90^\circ$ ).<sup>44</sup> Surface energies calculated for various Cu<sub>2</sub>Sb facets presented in Table S6† indicate that the (100) surface is the lowest energy facet. To simulate the catalytic active phases of Cu-Sb-S having low sulfur content, we considered nine active site motifs (Fig. S19b and c†) based on pristine Cu<sub>2</sub>Sb(100), with sulfur adatoms and substitutionally doped sulfur in the topmost and next atomic layer.

Due to possibilities of S-removal, we also considered three active site motifs with copper and antimony vacancies at the

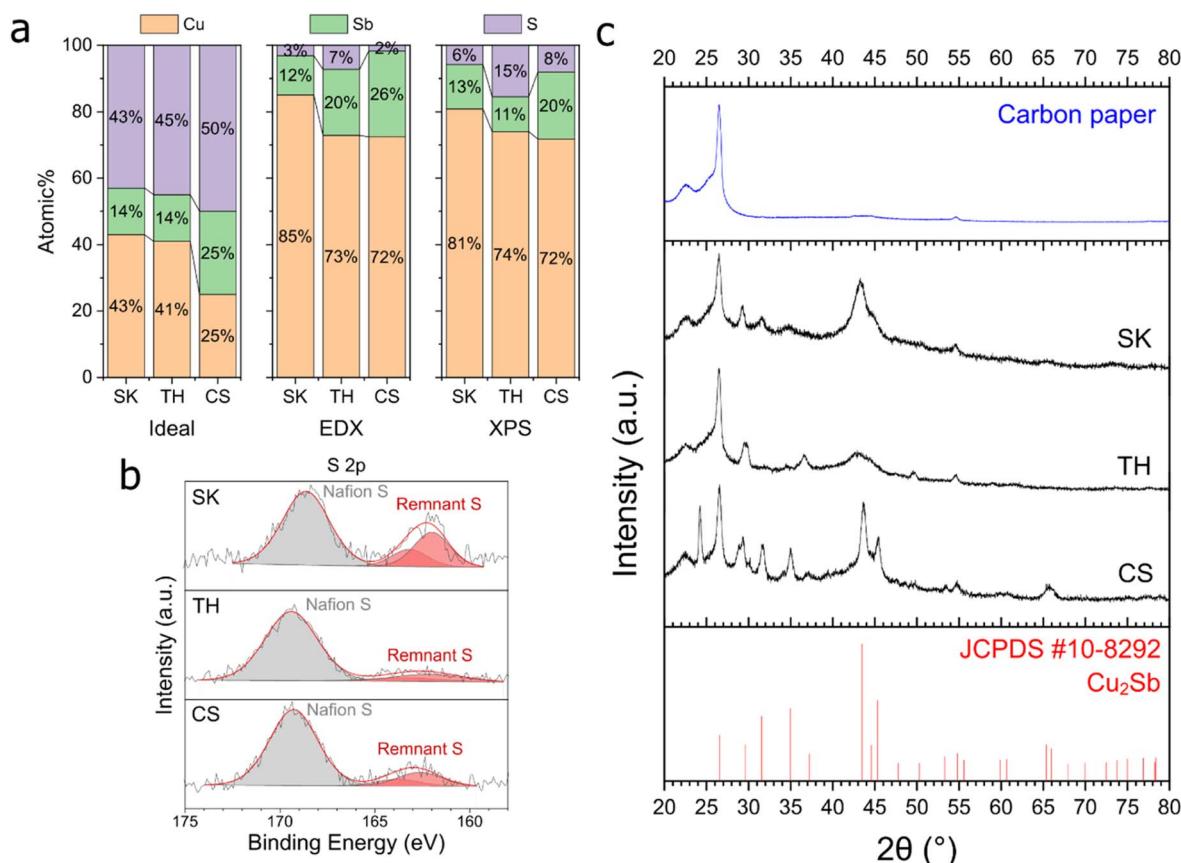


Fig. 6 EDX, XPS and XRD characterization of the samples after reduction. (a) Elemental composition of the samples on carbon paper. (b) XPS S 2p peaks of the samples on carbon paper. (c) XRD image of the samples with 9× loading on carbon paper. The reference peaks are that of Cu<sub>2</sub>Sb.

$\text{Cu}_1$ ,  $\text{Cu}_2$  and  $\text{Sb}_1$  sites (Fig. S19a†). We hence first investigated the stability of sulfur-decorated and vacancy surface motifs (ESI Section S5.2†). We found that  $\text{S}_{\text{Cu}_3}@\text{Cu}_2\text{Sb}(100)$  is not likely to be stable under operating conditions (Table S4†) and hence will not be considered further.

Then, we tested the adsorption of the four key intermediates:  $^*\text{H}$ ,  $^*\text{COOH}$ ,  $\text{HCOO}^*$  and  $^*\text{CO}$  involved in the 2e- $\text{CO}_2\text{RR}$  (additional details in ESI Section S5.4†). By comparing the adsorption energies on all surfaces against those on  $\text{Cu}_2\text{Sb}(100)$  (Table S5†), seven surfaces ( $\text{S}_{\text{Cu}_3}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_3\text{Sb}}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_1}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_1}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$ , and  $\text{V}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$ ) bind  $^*\text{CO}$  less strongly than both  $\text{Cu}(111)$  and  $\text{Cu}_2\text{Sb}(100)$ . It has been demonstrated that  $\text{CO}_2\text{RR}$  catalysts that are selective towards the  $2\text{e}^-$  products experimentally possess a  $^*\text{CO}$  binding energy that is weaker than that on  $\text{Cu}(111)$ .<sup>45</sup> The weaker binding of  $^*\text{CO}$  on the seven surfaces will promote  $^*\text{CO}$  desorption rather than further reduction to  $^*\text{CHO}$  or  $^*\text{COH}$ . Since the CS, SK, and TH samples showed a high selectivity towards the 2e- $\text{CO}_2\text{RR}$  products even at a more negative applied voltage of  $-1.2$  V, these seven active site motifs are more likely to be present in the catalytic active  $\text{Cu-Sb-S}$  phases.

With the remaining seven active site motifs, we employ a selectivity analysis towards CO or HCOOH formation similar to that adopted by Tang *et al.*<sup>24</sup> (additional details in ESI Section S5.5†). Essentially, a motif that provides a larger driving force for  $^*\text{COOH}$  formation ( $\Delta_{\text{R}1}G$  in eqn (S10)†) than for  $\text{HCOO}^*$  ( $\Delta_{\text{R}2}G$  in eqn (S11)†) is selective towards the CO pathway. If the converse is true, the active site is more selective towards HCOOH. Another important consideration is the availability of  $\text{H}^*$  for the formation of  $\text{HCOO}^*$ . This availability of  $\text{H}^*$  is given by using eqn (S12).† One can thus use  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  as a descriptor: a negative (positive) value indicates a larger driving force for the CO (HCOOH) pathway. The values for  $\Delta_{\text{R}1}G$ ,  $\Delta_{\text{R}2}G$ ,  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  and  $\Delta_{\text{R}3}G$  for the seven relevant active site motifs are in Table 1 while the values for all site motifs considered in this work are in Table S8.†

At an operating potential of  $-1.0$  V, all seven  $\text{Cu}_2\text{Sb}$ -based motifs indicate that the formation of  $^*\text{COOH}$  is thermodynamically favourable. We found that  $\text{Cu}_2\text{Sb}(100)$  is more

**Table 1** Selectivity metrics at an operating voltage of  $-1.0$  V. A negative (positive) value of  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  favours CO (formate) formation. The  $\Delta_{\text{R}3}G$  is used as a descriptor to define surface hydrogenation. A negative  $\Delta_{\text{R}3}G$  value favours surface hydrogenation

Surface structure	$\Delta_{\text{R}1}G$ (eV)	$\Delta_{\text{R}2}G$ (eV)	$\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$ (eV)	$\Delta_{\text{R}3}G$ (eV)
$\text{Cu}(111)$	-0.42	-0.28	-0.15	-1.17
$\text{Cu}_2\text{Sb}(100)$ , reference	-0.34	0.14	-0.48	-1.05
$\text{S}_{\text{Cu}_3}@\text{Cu}_2\text{Sb}(100)$	-0.30	0.36	-0.66	-0.92
$\text{S}_{\text{Cu}_3\text{Sb}}@\text{Cu}_2\text{Sb}(100)$	-0.15	0.24	-0.39	-0.86
$\text{S}_{\text{Cu}_1}@\text{Cu}_2\text{Sb}(100)$	-0.04	0.32	-0.36	-0.78
$\text{S}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$	-0.27	0.38	-0.65	-0.91
$\text{S}_{\text{Sb}_1}@\text{Cu}_2\text{Sb}(100)$	-0.23	0.15	-0.38	-0.94
$\text{V}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$	-0.25	0.33	-0.58	-1.08
$\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$	-0.71	-0.15	-0.56	-0.99

selective towards CO formation as compared to  $\text{Cu}(111)$  due to a more negative  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  value.  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  values on the other seven motifs are negative, indicating that the CO pathway is thermodynamically favoured. In fact, the  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  values on  $\text{S}_{\text{Cu}_3}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_3\text{Sb}}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{V}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$ , and  $\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$  are more negative than that on  $\text{Cu}_2\text{Sb}(100)$ . The higher CO selectivity in  $\text{Cu}_2\text{Sb}$ -based motifs can be ascribed to a weaker  $\text{H}^*$  adsorption, which leads to a more positive  $\Delta_{\text{R}2}G$  value and thus a more negative  $\Delta_{\text{R}1}G - \Delta_{\text{R}2}G$  value. One finds that  $\text{H}^*$  adsorption is 0.12 eV weaker on  $\text{Cu}_2\text{Sb}(100)$  than on  $\text{Cu}(111)$  and this  $\text{H}^*$  adsorption strength can be further modulated by the presence of sulfur. In fact, we noticed that the presence of sulfur in the six S-decorated motifs (*i.e.*,  $\text{S}_{\text{Cu}_3}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_3\text{Sb}}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_1}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_1}@\text{Cu}_2\text{Sb}(100)$ , and  $\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$ ) further weakens  $\text{H}^*$  adsorption as compared with that on  $\text{Cu}_2\text{Sb}(100)$ . We note from adsorption data in Table S5† that  $\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$  binds  $\text{HCOO}^*$  stronger than  $\text{Cu}_2\text{Sb}(100)$  while the five other motifs with sulfur as an adatom or as a substitutional dopant in the topmost layer bind  $\text{HCOO}^*$  weaker. The simultaneous weakening of  $\text{H}^*$  adsorption and  $\text{HCOO}^*$  in turn results in positive  $\Delta_{\text{R}2}G$  values for  $\text{S}_{\text{Cu}_3}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_3\text{Sb}}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_1}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$  and  $\text{S}_{\text{Sb}_1}@\text{Cu}_2\text{Sb}(100)$ . On the other hand, the enhancement of  $\text{HCOO}^*$  adsorption is greater than the weakening of  $\text{H}^*$ , hence giving an overall negative  $\Delta_{\text{R}2}G$  value for  $\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$ . While these seven  $\text{Cu}_2\text{Sb}$ -based motifs are all selective towards CO formation, HCOOH and  $\text{H}_2$  were also produced in the electrochemical tests. We rationalize these pathways with the Gibbs energy diagrams in the next section.

From the seven sites shortlisted from the reactivity analysis, sulfur stability analysis (ESI Section S5.2†) was carried out to narrow the list down further to four surface motifs that are most likely to be present throughout the electrochemical operation: pristine  $\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_1}@\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_2}@\text{Cu}_2\text{Sb}(100)$  and  $\text{V}_{\text{Cu}_2}@\text{Cu}_2\text{Sb}(100)$ . These four surface motifs are expected to be stable at  $-1.0$  V and adsorb  $^*\text{CO}$  weaker than  $\text{Cu}(111)$  to form only 2e- $\text{CO}_2\text{RR}$  products. We finally plotted the Gibbs energy diagrams at 0 V and  $-1.0$  V to have an overview of the CO pathway (eqn (S13)–(S15)†), HCOOH pathway (eqn (S16)–(S18)†) and hydrogen evolution reaction (HER) (eqn (S19) and (S20)†) in Fig. 7 respectively. The Gibbs energy diagrams for all the surface motifs considered at 0.0 V can be found in Fig. S21.† We tabulated the Gibbs energy changes for the CO, HCOOH and HER pathways at 0.0 V in Tables S9–S11† respectively.

Before we discuss the  $\text{CO}_2\text{RR}$  pathways, we first evaluated the HER performance by using different surface models. We included  $\text{Pt}(111)$ , which is known to be the best prototypical electrocatalyst towards the HER ( $\Delta G(^*\text{H}) = -0.38$  eV). Although all the four surface motifs perform worse than  $\text{Pt}(111)$ , the HER is exergonic at  $-1.0$  V, which is why  $\text{H}_2$  is always produced.

Moving to the CO pathway, we find from the Gibbs energy diagrams at 0.0 V in Fig. 7 that the potential determining step is the electrochemical hydrogenation of  $\text{CO}_2$  to  $^*\text{COOH}$  for  $\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_1}$ ,  $\text{V}_{\text{Cu}_2}$  and  $\text{S}_{\text{Sb}_2}$ . This is consistent with the finding for the CO Tafel slopes shown in Fig. 5, with values close to 120 mV dec<sup>-1</sup> for the three catalytic active phases. This Tafel

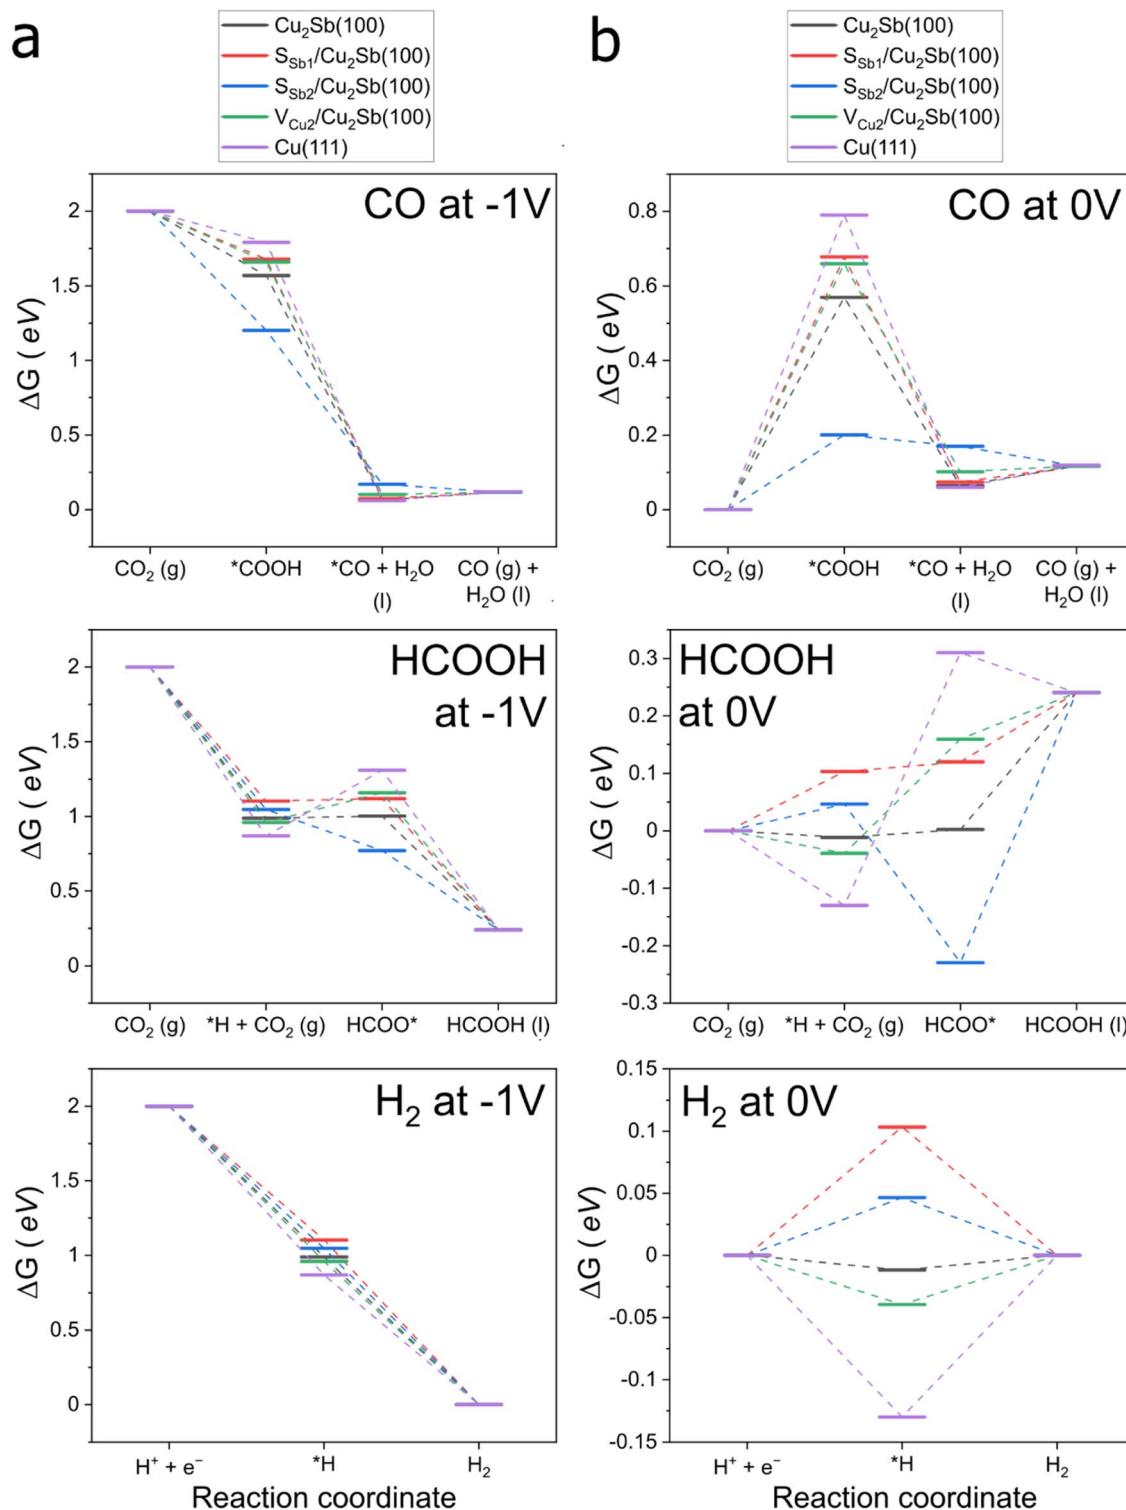


Fig. 7 Free energy diagrams of four surface sites on  $\text{Cu}_2\text{Sb}(100)$ . The potentials are displayed for (a)  $-1.0$  V vs. RHE to represent experimental conditions and (b)  $0$  V vs. RHE to show the potential determining step (PDS). The data are displayed for CO, HCOOH and  $\text{H}_2$  pathways. Note that the energy level of each energy state in eV is affected by the applied potential such that they are shifted by the negative of the product of the number of electrons involved ( $n_e$ ) and the applied potential vs. RHE ( $U$ ). Hence, at an applied potential of  $-1.0$  V vs. RHE, each energy state is shifted by  $+1.0n_e$  eV.

slope indicates that the rate determining step is an electrochemical step, which is unlikely to be  $^*\text{CO}$  desorption. At  $-1.0$  V, the hydrogenation of  $\text{CO}_2$  to  $^*\text{COOH}$  for the four motifs is exergonic. The desorption of  $^*\text{CO}$  is expected to involve an energy barrier of less than  $0.10$  eV that was easily overcome.

From the free energy diagrams for the  $\text{HCOOH}$  pathway at  $0.0$  V, we found that in general, the PDS for  $\text{HCOOH}$  formation is the chemical step involving hydrogenation of  $\text{CO}_2$  to form  $\text{HCOO}^*$ . The exception being  $\text{S}_{\text{Sb}_2}/\text{Cu}_2\text{Sb}(100)$ , on which the hydrogenation of  $\text{HCOO}^*$  is potential limiting. At  $-1.0$  V, the  $\text{HCOOH}$  pathway on  $\text{S}_{\text{Sb}_2}/\text{Cu}_2\text{Sb}(100)$  is exergonic for all elementary steps. This means that  $\text{S}_{\text{Sb}_2}/\text{Cu}_2\text{Sb}(100)$  can produce both  $\text{CO}$  and  $\text{HCOOH}$ , consistent with the negative values of  $\Delta_{\text{R}1}G$  and  $\Delta_{\text{R}2}G$  presented earlier. It was noted that  $\text{HCOOH}$  was always produced in the electrochemical tests at  $-1.0$  V. We found that the energy barrier of the potential determining step for the  $\text{HCOOH}$  pathway on pristine  $\text{Cu}_2\text{Sb}(100)$ ,  $\text{S}_{\text{Sb}_2}/\text{Cu}_2\text{Sb}(100)$  and  $\text{V}_{\text{Cu}_2}/\text{Cu}_2\text{Sb}(100)$  surface motifs only require  $0.01$  eV,  $0.02$  eV and  $0.20$  eV at  $-1.0$  V, which can be overcome under ambient conditions. Since the pristine  $\text{Cu}_2\text{Sb}(100)$  surface motif should predominate in the three samples CS, SK and TH, such a barrier can be overcome which explains why  $\text{HCOOH}$  was always produced in the electrochemical tests at  $-1.0$  V just like  $\text{H}_2$ .

Overall, the computational results are consistent with the experimental results, which showed a high selectivity towards the  $2\text{e-}\text{CO}_2\text{RR}$  products even at a more negative applied voltage of  $-1.0$  V. The results also help explain why the TH phase retains the highest percentage of sulfur after electrochemical tests, and they provide insight into the active phase and surfaces involved in the  $2\text{e-}\text{CO}_2\text{RR}$  process.

## Conclusions

In summary, sulfide-derived Cu-Sb electrocatalysts for  $\text{CO}_2$  reduction have been studied in a GDE-based cell. Three-different Cu-Sb-S phases were synthesized by a heat-up colloidal nanoparticle route which demonstrated different selectivity for the  $\text{CO}_2\text{RR}$  with  $\text{CO}$  as the main product. Based on elemental composition characterization after reduction, we have shown that these different selectivity patterns were due to the different elemental compositions when the parent phases are reduced. Less Cu minimizes phase segregation into detrimental S-doped Cu which forms  $\text{HCOO}^-$  and  $\text{H}_2$ , while more sulfur disrupts crystallinity and encourages  $\text{CO}$  formation. This is seen in the TH sample having the highest residual sulfur and demonstrating the highest CO FE of about  $80.5\%$  at  $-1.0$  V with a geometric partial current density of  $37.6\text{ mA cm}^{-2}$ . DFT calculations show that substitution of Sb sites with S likely contributes to this improved performance. These findings run contrary to the expectation that sulfide-derived electrocatalysts for the  $\text{CO}_2\text{RR}$  encourage  $\text{HCOO}^-$ , which has been the case for most of the studies in this category so far. This study challenges this assumption and could likely open the door to studies on other chalcogenides with surprising selectivity patterns and could also point the way to engineering better catalysts to produce CO in sulfur-rich environments such as the flue gas  $\text{CO}_2\text{RR}$ .<sup>46</sup>

## Methods

### Synthesis of nanoparticles

We synthesized three of the four major phases of the copper antimony sulfide (Cu-Sb-S) system: skinnerite (SK;  $\text{Cu}_3\text{SbS}_3$ ), tetrahedrite (TH;  $\text{Cu}_{12}\text{Sb}_4\text{S}_{13}$ ), and chalcostibite (CS;  $\text{CuSbS}_2$ )<sup>34,47</sup> that have different Cu/Sb/S stoichiometric ratios. These phases were synthesized by a heat-up colloidal nanoparticle route as follows:

- For SK,  $\text{Cu}_3\text{SbS}_3$ ,  $3.75$  mmol of copper(II) acetylacetone,  $1.25$  mmol of antimony(III) acetate,  $3$  mL of 1-dodecanethiol and  $3$  mL of oleylamine were dissolved in  $24$  mL of 1-octadecene in a  $250$  mL three-neck flask and the mixture was degassed under flowing nitrogen for  $30$  min at  $150$  °C. The mixture was then heated to  $220$  °C for  $1$  h under a nitrogen atmosphere for the formation of nanoparticles.

- For TH,  $\text{Cu}_{12}\text{Sb}_4\text{S}_{13}$ ,  $3.75$  mmol of copper(II) acetylacetone,  $1.25$  mmol of antimony(III) acetate,  $3$  mL of 1-dodecanethiol and  $3$  mL of oleylamine were dissolved in  $24$  mL of 1-octadecene in a  $250$  mL three-neck flask and the mixture was degassed under flowing nitrogen for  $30$  min at  $150$  °C. The mixture was then heated to  $260$  °C for  $1$  h under a nitrogen atmosphere for the formation of nanoparticles.

- For CS,  $\text{CuSbS}_2$ ,  $2$  mmol of copper(II) acetylacetone,  $2$  mmol of antimony(III) acetate,  $3$  mL of 1-dodecanethiol and  $3$  mL of oleylamine were dissolved in  $24$  mL of 1-octadecene in a  $250$  mL three-neck flask and the mixture was degassed under flowing nitrogen for  $30$  min at  $150$  °C. The mixture was then heated to  $250$  °C for  $1$  h under a nitrogen atmosphere for the formation of nanoparticles.

The resulting suspensions are then topped up to  $45$  mL with ethanol, sonicated and centrifuged at  $10\,000$  rpm for  $5$  min using a Thermo Scientific Sorvall Legend x1. Then, the nanoparticles are centrifuged in ethanol for the removal of polar impurities. Subsequently, the nanoparticles are centrifuged three times with a hexane/ethanol mixture in  $25:20$ ,  $15:30$  and  $5:40$  mL ratios for the removal of organic impurities.

The  $\text{CuSbS}_2$  powder is additionally immersed in  $0.5$  M NaOH for  $30$  min and centrifuged to etch  $\text{Sb}_2\text{S}_3$  impurities, followed by centrifugation in deionized water to remove the remaining NaOH.

Finally, the nanoparticles are centrifuged in isopropyl alcohol and dried in an oven at  $70$  °C for an hour.

### Preparation of the catalyst layer on gas diffusion electrodes

$27$  mg of the catalyst was dispersed in  $2$  mL of ethanol with  $100$   $\mu\text{l}$  of nafton ionomer solution (5%) and ultrasonicated for  $30$  min. The prepared catalyst ink was then airbrushed with an airbrush gun (Paasche) onto a  $6 \times 6\text{ cm}^2$  CeTech (CT) GDL280 carbon paper.

### Electrochemical measurements in a three-compartment flow cell

The electrochemical measurements were carried out in a three-compartment gas diffusion electrode (GDE) flow cell,<sup>48</sup> with an anion exchange membrane (Fumasep FAA-3-pk-130) and nickel

foam clamped between the catholyte and anolyte compartments and carbon paper with catalyst ink clamped between the gas and catholyte compartments. The geometric area of the working electrode was 1 cm<sup>2</sup>. The reference electrode placed in the catholyte compartment was an AgCl electrode filled with 3 M KCl.

The applied voltage was compensated for 80% of the measured *iR* drop using an Autolab PGSTAT302N. The resulting voltage was then converted to the RHE scale using the formula:

$$E_{\text{RHE}} = E_{\text{Ag/AgCl}} + 0.197 + 0.0591 \times \text{pH} \quad (1)$$

Chronoamperometry experiments were carried out with an Autolab PGSTAT302N, with an Alicat MC-100SCCM-D mass flow controller to control the flow of CO<sub>2</sub> to the gas inlet. A mass flow of 40 sccm was used for all experiments. 25 mL of catholyte and 25 mL of anolyte were used, pumped at a rate of 28.5 mL min<sup>-1</sup>. Gas products were quantified with a gas chromatograph (Shimadzu Nexis GC-2030) equipped with a thermal conductivity detector (TCD) and flame ionization detector (FID) with an optional methanizer setting. Liquid products were quantified with a liquid chromatograph (Shimadzu LC-2030) equipped with a UV detector and a refractive index detector (RID).

The faradaic efficiency (gas product) was calculated with the equation:

$$\text{FE}(\%) = \frac{\text{conc(ppm)} \times 40 \text{ sccm} \times 2e^-}{1000000 \times 24000 \text{ cm}^3 \text{ L}^{-1} \times 60 \text{ s}} \div \frac{\text{current(A)}}{96485 \text{ C mol}^{-1}} \quad (2)$$

The faradaic efficiency (liquid product) was calculated with the equation:

$$\text{FE}(\%) = \frac{\text{conc(mmol L}^{-1}) \times 0.050 \text{ L} \times 2e^-}{1000} \div \frac{\text{charge(C)}}{96485 \text{ C mol}^{-1}} \quad (3)$$

### Catalyst characterization

X-ray diffraction (XRD) was carried out using a Panalytical X'Pert Pro with Cu-K $\alpha$  radiation operated at 40 kV and 30 mA. Field emission scanning electron microscopy (FE-SEM) images were taken using a JEOL JSM-7600F equipped with an INCA - XAct 10 mm<sup>2</sup> X-ray detector for energy-dispersive X-ray (EDX) analysis. Transmission electron microscopy (TEM) was obtained using a JEOL 2100F. X-ray photoelectron spectroscopy (XPS) data were collected using a Kratos AXIS Supra.

### DFT calculations

All density functional theory calculations were performed using Quantum ESPRESSO<sup>49,50</sup> within an atomic simulation environment (ASE). Core electrons were represented using Vanderbilt ultra-soft pseudopotentials.<sup>51</sup> A plane wave basis set with a kinetic energy and density cut-off of 500 eV and 5000 eV, respectively, were used. A Fermi-level smearing width of 0.1 eV was adopted to accelerate the convergence of metallic systems. The Perdew–Burke–Ernzerhof (PBE) exchange–correlation

functional was adopted.<sup>52</sup> Long range dispersion corrections were accounted for using Grimme's D3 approach.<sup>53</sup> The convergence criteria for the total energy and Hellmann–Feynman force per atom set were at 10<sup>-6</sup> eV and 0.05 eV Å<sup>-1</sup> respectively.

The primitive cell was used for the calculation of bulk Cu, Pt, Sb and Cu<sub>2</sub>Sb and they were sampled with (8,8,8), (8,8,8), (8,8,8), and (6,6,4) *k*-point grids, respectively, in the first Brillouin zone generated in the Monkhorst–Pack scheme.<sup>54</sup> The primitive cell of the three parent phases chalcostibite (CS), skinnerite (SK) and tetrahedrite (TH) were also used, sampled with (6,4,2), (4,3,2), and (3,3,3) Monkhorst–Pack grids, respectively.

We created orthogonal asymmetric slabs encompassing only the surface primitive cell of different facets of Cu<sub>2</sub>Sb to calculate the surface energies. The number of atomic layers used and fixed in the asymmetric slabs are tabulated in Table S6† along with the lateral lattice parameters, (*a* and *b*), the surface area of the cell, and the surface energy. The surface primitive cells of (100), (101), (110) and (001) were sampled with (6,4,1), (4,6,1), (4,4,1), and (6,6,1) Monkhorst–Pack grids, respectively.

All gas-phase species were calculated in a 21 Å × 22 Å × 23 Å simulation cell sampled with the  $\Gamma$ -point. The surface slabs of Cu(111), Pt(111), Cu<sub>2</sub>Sb(100) and Cu<sub>2</sub>Sb(101) were constructed as (3 × 3 × 4), (3 × 3 × 4), (3 × 2 × 6), and (2 × 2 × 6) with the bottom two atomic layers fixed to their bulk positions. These surface slabs were sampled using (3,3,1), (3,3,1), (3,4,1), and (3,3,1) *k*-point grids, respectively. A vacuum of at least 15 Å and a dipole correction were included in the direction perpendicular to the surface to mitigate spurious electrostatic interactions for all surface calculations.<sup>55</sup>

Additional information, including surface energy calculations (Table S6†) and the gas-phase and adsorbate Gibbs energy correction adopted for this work (Table S7†) can be found in the ESI.†

### Author contributions

D. Y. Y. G., Y. L. and L. H. W. conceived the study. J. M. R. T. designed the heat-up colloidal synthesis procedure and D. Y. Y. G. carried out the synthesis. D. Y. Y. G. carried out the electrochemical testing, most of the characterization and analyzed the experimental data. Y. W. carried out the TEM characterization. K. M. Y., R. L. and T. S. C. carried out the DFT modelling. Y. L. and L. H. W. supervised the project, while A. D. H. and Y. C. T. contributed to the discussion of the data and the writing of the manuscript.

### Conflicts of interest

There are no conflicts to declare.

### Acknowledgements

This research was financially supported by grants from the National Research Foundation, Prime Minister's Office, Singapore, under its Campus of Research Excellence and Technological Enterprise (CREATE) program as well as the Singapore

Ministry of Education (MOE) Tier 1 grant (Award ID RG68/21), Tier 2 grant (MOE T2EP50120-0008) and Agency for Science, Technology and Research (A\*STAR) Career Development Award (Project No. 202D800037). We thank Mengyuan Zhang for the initial discussion on this project. We acknowledge the Facility for Analysis, Characterisation, Testing and Simulation, Nanyang Technological University, Singapore, for use of their electron microscopy/X-ray facilities, with thanks to Weiling Liu and Teddy Salim for their help in XPS. We also thank Anqi Sng of the Institute of Materials Research and Engineering, A\*STAR for her help in performing ICP measurements. K. M. Y., L. R., and T. S. C acknowledge the financial support of the Singapore National Research Foundation (NRF) through the Campus for Research Excellence and Technological Enterprise (CREATE) programme, and from the Ministry of Education Academic Research Fund Tier-1: RG5/22. We thank the High Performance Computing (HPC) team at the HPC Centre, Nanyang Technological University (NTU) for technical assistance and computing resources. The computational work for this article was partially performed on resources of the National Supercomputing Centre, Singapore (<https://www.nscc.sg/>). This work used computational resources of the supercomputer Fugaku provided by Riken through the HPCI system research project (Project ID: hp220158). L. R. acknowledges NTU for a research scholarship. D. Y. Y. G. wishes to thank Zheng Hao Tan, Ying Fan Tay, Surani bin Dolmanan, Meltem Yilmaz, Mahmoud Ahmed, Vincent and Roong Jien Wong for helpful discussions.

## References

- 1 J. Gao, C. Jia and B. Liu, *Catal. Sci. Technol.*, 2017, **7**, 5602–5607.
- 2 S. Nitopi, E. Bertheussen, S. B. Scott, X. Liu, A. K. Engstfeld, S. Horch, B. Seger, I. E. L. Stephens, K. Chan, C. Hahn, J. K. Nørskov, T. F. Jaramillo and I. Chorkendorff, *Chem. Rev.*, 2019, **119**, 7610–7672.
- 3 X. Jiang, X. Nie, X. Guo, C. Song and J. G. Chen, *Chem. Rev.*, 2020, **120**, 7984–8034.
- 4 C. Chen, J. F. Khosrowabadi Kotyk and S. W. Sheehan, *Chem.*, 2018, **4**, 2571–2586.
- 5 H. Shin, K. U. Hansen and F. Jiao, *Nat. Sustainability*, 2021, **4**, 911–919.
- 6 C. W. Li, J. Ciston and M. W. Kanan, *Nature*, 2014, **508**, 504–507.
- 7 Y. Lum and J. W. Ager, *Angew. Chem., Int. Ed.*, 2018, **57**, 551–554.
- 8 D. Gao, I. Zegkinoglou, N. J. Divins, F. Scholten, I. Sinev, P. Grosse and B. Roldan Cuenya, *ACS Nano*, 2017, **11**, 4825–4831.
- 9 A. D. Handoko, C. W. Ong, Y. Huang, Z. G. Lee, L. Lin, G. B. Panetti and B. S. Yeo, *J. Phys. Chem. C*, 2016, **120**, 20058–20067.
- 10 L. C. Pardo Pérez, A. Arndt, S. Stojkovicj, I. Y. Ahmet, J. T. Arens, F. Dattila, R. Wendt, A. Guilherme Buzanich, M. Radtke, V. Davies, K. Höflich, E. Köhnen, P. Tockhorn, R. Golnak, J. Xiao, G. Schuck, M. Wollgarten, N. López and M. T. Mayer, *Adv. Energy Mater.*, 2022, **12**, 2103328.
- 11 W. Zhu, B. M. Tackett, J. G. Chen and F. Jiao, *Top. Curr. Chem.*, 2018, **376**, 41.
- 12 Y. Wu, S. Cao, J. Hou, Z. Li, B. Zhang, P. Zhai, Y. Zhang and L. Sun, *Adv. Energy Mater.*, 2020, **10**, 2000588.
- 13 H. Song, Y. C. Tan, B. Kim, S. Ringe and J. Oh, *ACS Appl. Mater. Interfaces*, 2021, **13**, 55272–55280.
- 14 L. Wang, H. Peng, S. Lamaison, Z. Qi, D. M. Koshy, M. B. Stevens, D. Wakerley, J. A. Zamora Zeledón, L. A. King, L. Zhou, Y. Lai, M. Fontecave, J. Gregoire, F. Abild-Pedersen, T. F. Jaramillo and C. Hahn, *Chem. Catal.*, 2021, **1**, 663–680.
- 15 A. Mukherjee, M. Abdinejad, S. S. Mahapatra and B. C. Ruidas, *J. Mater. Chem. A*, 2023, **11**, 9300–9332.
- 16 W. Ma, S. Xie, X.-G. Zhang, F. Sun, J. Kang, Z. Jiang, Q. Zhang, D.-Y. Wu and Y. Wang, *Nat. Commun.*, 2019, **10**, 892.
- 17 X. Zheng, P. De Luna, F. P. García de Arquer, B. Zhang, N. Becknell, M. B. Ross, Y. Li, M. N. Banis, Y. Li, M. Liu, O. Vozny, C. T. Dinh, T. Zhuang, P. Stadler, Y. Cui, X. Du, P. Yang and E. H. Sargent, *Joule*, 2017, **1**, 794–805.
- 18 T. Shinagawa, G. O. Larrazábal, A. J. Martín, F. Krumeich and J. Pérez-Ramírez, *ACS Catal.*, 2018, **8**, 837–844.
- 19 K. R. Phillips, Y. Katayama, J. Hwang and Y. Shao-Horn, *J. Phys. Chem. Lett.*, 2018, **9**, 4407–4412.
- 20 Y. Huang, Y. Deng, A. D. Handoko, G. K. L. Goh and B. S. Yeo, *ChemSusChem*, 2018, **11**, 320–326.
- 21 W. Luc, B. H. Ko, S. Kattel, S. Li, D. Su, J. G. Chen and F. Jiao, *J. Am. Chem. Soc.*, 2019, **141**, 9902–9909.
- 22 Y. Deng, Y. Huang, D. Ren, A. D. Handoko, Z. W. Seh, P. Hirunsit and B. S. Yeo, *ACS Appl. Mater. Interfaces*, 2018, **10**, 28572–28581.
- 23 R. García-Muelas, F. Dattila, T. Shinagawa, A. J. Martín, J. Pérez-Ramírez and N. López, *J. Phys. Chem. Lett.*, 2018, **9**, 7153–7159.
- 24 M. T. Tang, H. Peng, P. S. Lamoureux, M. Bajdich and F. Abild-Pedersen, *Appl. Catal., B*, 2020, **279**, 119384.
- 25 R. Kortlever, J. Shen, K. J. P. Schouten, F. Calle-Vallejo and M. T. M. Koper, *J. Phys. Chem. Lett.*, 2015, **6**, 4073–4082.
- 26 H.-K. Lim, H. Shin, W. A. Goddard, Y. J. Hwang, B. K. Min and H. Kim, *J. Am. Chem. Soc.*, 2014, **136**, 11355–11361.
- 27 S. D. Deshmukh, R. G. Ellis, D. S. Sutandar, D. J. Rokke and R. Agrawal, *Chem. Mater.*, 2019, **31**, 9087–9097.
- 28 X.-L. Zhang, P.-C. Yu, X.-Z. Su, S.-J. Hu, L. Shi, Y.-H. Wang, P.-P. Yang, F.-Y. Gao, Z.-Z. Wu, L.-P. Chi, Y.-R. Zheng and M.-R. Gao, *Sci. Adv.*, 2023, **9**, eadh2885.
- 29 H.-i. Nam, K. Ryeol Park, Y.-W. Choi, H.-j. Sim, K. Yong Sohn and D.-H. Lim, *Appl. Surf. Sci.*, 2023, **612**, 155646.
- 30 S. Liu, H. Tao, Q. Liu, Z. Xu, Q. Liu and J.-L. Luo, *ACS Catal.*, 2018, **8**, 1469–1475.
- 31 Y. Lai, R. J. R. Jones, Y. Wang, L. Zhou, M. H. Richter and J. Gregoire, *J. Mater. Chem. A*, 2019, **7**, 26785–26790.
- 32 S. Rasul, D. H. Anjum, A. Jedidi, Y. Minenkov, L. Cavallo and K. Takanabe, *Angew. Chem., Int. Ed.*, 2015, **54**, 2146–2150.
- 33 S. Sarfraz, A. T. Garcia-Esparza, A. Jedidi, L. Cavallo and K. Takanabe, *ACS Catal.*, 2016, **6**, 2842–2851.
- 34 K. Ramasamy, H. Sims, W. H. Butler and A. Gupta, *Chem. Mater.*, 2014, **26**, 2891–2899.

35 T. J. Whittles, T. D. Veal, C. N. Savory, A. W. Welch, F. W. de Souza Lucas, J. T. Gibbon, M. Birkett, R. J. Potter, D. O. Scanlon, A. Zakutayev and V. R. Dhanak, *ACS Appl. Mater. Interfaces*, 2017, **9**, 41916–41926.

36 C. H. M. van Oversteeg, F. E. Oropeza, J. P. Hofmann, E. J. M. Hensen, P. E. de Jongh and C. de Mello Donega, *Chem. Mater.*, 2019, **31**, 541–552.

37 S. Mou, Y. Li, L. Yue, J. Liang, Y. Luo, Q. Liu, T. Li, S. Lu, A. M. Asiri, X. Xiong, D. Ma and X. Sun, *Nano Res.*, 2021, **14**, 2831–2836.

38 H. Li, T.-W. Jiang, X. Qin, J. Chen, X.-Y. Ma, K. Jiang, X.-G. Zhang and W.-B. Cai, *ACS Catal.*, 2021, **11**, 6846–6856.

39 Y. Li, S. Chu, H. Shen, Q. Xia, A. W. Robertson, J. Masa, U. Siddiqui and Z. Sun, *ACS Sustain. Chem. Eng.*, 2020, **8**, 4948–4954.

40 C. W. Lee, N. H. Cho, S. W. Im, M. S. Jee, Y. J. Hwang, B. K. Min and K. T. Nam, *J. Mater. Chem. A*, 2018, **6**, 14043–14057.

41 E. M. Espinoza, J. A. Clark, J. Soliman, J. B. Derr, M. Morales and V. I. Vullev, *J. Electrochem. Soc.*, 2019, **166**, H3175–H3187.

42 N. Elgrishi, K. J. Rountree, B. D. McCarthy, E. S. Rountree, T. T. Eisenhart and J. L. Dempsey, *J. Chem. Educ.*, 2018, **95**, 197–206.

43 Y.-G. Kim, J. H. Baricuatro and M. P. Soriaga, *Electrocatalysis*, 2018, **9**, 526–530.

44 W. B. Pearson, *Z Kristallogr Cryst Mater.*, 1985, **171**, 23–40.

45 K. P. Kuhl, T. Hatsukade, E. R. Cave, D. N. Abram, J. Kibsgaard and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2014, **136**, 14107–14113.

46 B.-U. Choi, Y. C. Tan, H. Song, K. B. Lee and J. Oh, *ACS Sustain. Chem. Eng.*, 2021, **9**, 2348–2357.

47 B. J. Skinner, F. D. Luce and E. Makovicky, *Econ. Geol.*, 1972, **67**, 924–938.

48 Y. C. Tan, W. K. Quek, B. Kim, S. Sugiarto, J. Oh and D. Kai, *ACS Energy Lett.*, 2022, **7**, 2012–2023.

49 P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari and R. M. Wentzcovitch, *J. Phys.: Condens. Matter*, 2009, **21**, 395502.

50 P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. Buongiorno Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, N. Colonna, I. Carnimeo, A. Dal Corso, S. de Gironcoli, P. Delugas, R. A. DiStasio, A. Ferretti, A. Floris, G. Fratesi, G. Fugallo, R. Gebauer, U. Gerstmann, F. Giustino, T. Gorni, J. Jia, M. Kawamura, H. Y. Ko, A. Kokalj, E. Küçükbenli, M. Lazzeri, M. Marsili, N. Marzari, F. Mauri, N. L. Nguyen, H. V. Nguyen, A. Otero-de-la-Roza, L. Paulatto, S. Poncé, D. Rocca, R. Sabatini, B. Santra, M. Schlipf, A. P. Seitsonen, A. Smogunov, I. Timrov, T. Thonhauser, P. Umari, N. Vast, X. Wu and S. Baroni, *J. Phys.: Condens. Matter*, 2017, **29**, 465901.

51 D. Vanderbilt, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1990, **41**, 7892–7895.

52 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.

53 E. Caldeweyher, S. Ehlert, A. Hansen, H. Neugebauer, S. Spicher, C. Bannwarth and S. Grimme, *J. Chem. Phys.*, 2019, **150**, 154122.

54 H. J. Monkhorst and J. D. Pack, *Phys. Rev. B: Solid State*, 1976, **13**, 5188–5192.

55 L. Bengtsson, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 12301–12304.