



Cite this: *RSC Adv.*, 2017, 7, 36594

The effect of reduced graphene oxide on the catalytic activity of Cu–Cr–O–TiO₂ to enhance the thermal decomposition rate of ammonium perchlorate: an efficient fuel oxidizer for solid rocket motors and missiles

Harish Kumar,[†] Prahald N. Tengli,^c Vijay Kumar Mishra,^{†*} Pankaj Tripathi,^e Awani Bhushan^f and Pradeep Kumar Mishra^a

Reduced graphene oxide (rGO) modified transition metal oxide based composites were successfully synthesized *via* a sol–gel assisted Hummers' method. The present study includes the synthesis of CuCr₂O₄·0.7TiO₂, the synthesis of rGO and the synthesis of rGO modified CuCr₂O₄·0.7TiO₂. In order to synthesize the desired catalyst, rGO and Cu–Cr–O–0.7TiO₂ were synthesized individually. The CuCr₂O₄·0.7TiO₂ composite was synthesized *via* a sol–gel method. Reduced graphene oxide (rGO) used as a modifier in the catalyst, was also synthesized in the laboratory and was calcined at high temperature (1050 °C) to improve its activity. Finally, Cu–Cr–O–0.7TiO₂ was modified with 10 wt% rGO. The post synthesis characterizations were performed using various instrumental techniques including X-ray diffraction (XRD) for phase analysis, Fourier transform infrared (FTIR) and Raman spectroscopy for molecular interactions, scanning electron microscopy (SEM) for surface morphology, energy dispersive X-ray analysis (EDX), elemental analysis and X-ray photoelectron spectroscopy (XPS) for binding energy. The catalytic efficiency of the synthesized composite catalyst samples based thermal decomposition of the host material (*i.e.* AP) was determined by differential thermal analysis (DTA) and thermogravimetric analysis (TGA). The rGO modification into the Cu–Cr–O–0.7TiO₂ tri-metallic composition made it the most promising catalyst for the thermal decomposition of AP, due to the tremendously high electrical and thermal conductivity of rGO. Different amounts (2.5, 5.0, 7.5 and 10 wt%) of Cu–Cr–O–0.7TiO₂–rGO were added to ammonium perchlorate (AP) to investigate its effect on the thermal decomposition of AP, which is a well known oxidizer used worldwide in the solid composite propellant (SCP) in modern rocketry. The 5 wt% of catalyst (Cu–Cr–O–0.7TiO₂–rGO) addition into AP exhibited the remarkably enhanced thermal decomposition of AP. Finally, the burn rate of SCP was examined with 5 wt% catalyst modified AP. The 5 wt% of catalyst modified AP exhibited 175.31% higher burn rate of SCP, compared to the burn rate of pure AP added SCP. Furthermore, when it was compared with an industrial catalyst, *i.e.* activated copper chromite (ACR), it showed 133.61% higher burn rate of SCP. The SCP exhibited excellent ballistic performance with 0.6% of catalyst in AP, which enhanced the burn rate from 4.866 mm s⁻¹ (for SCP having pure AP) to 8.531 mm s⁻¹ (for SCP having catalyst added AP) and 6.385 mm s⁻¹ (for SCP having industrial catalyst added AP) at 33 bar.

Received 29th May 2017

Accepted 6th July 2017

DOI: 10.1039/c7ra06012b

rsc.li/rsc-advances

^aDepartment of Chemical Engineering and Technology, Indian Institute of Technology (Banaras Hindu University), Varanasi-221005, India

^bSF Complex, Defence Research and Development Organization, Jagdalpur-494001, India

^cAeronautical Systems, Defence Research and Development Organization, Bangalore-560075, India

^dDepartment of Physics, Institute of Science, Banaras Hindu University, Varanasi-221005, India. E-mail: vijaybioceramic@gmail.com; Tel: +91-9452747012

^eDepartment of Ceramic Engineering, Indian Institute of Technology, (Banaras Hindu University), Varanasi-221005, India

^fDepartment of Mechanical Engineering, Indian Institute of Technology, (Banaras Hindu University), Varanasi-221005, India

[†] Present Address: Defence Materials and Stores Research and Development Establishment (DMSRDE), Defence Research and Development Organization, (DRDO) G. T. Road Kanpur-208013, India.

^{*} Present Address: Endocrinology Division, CSIR-Central Drug Research Institute, Lucknow-226031, India.



1. Introduction

Solid composite propellant (SCP) is the most reliable energy source in the era of solid rocket motors. SCP is composed of metallic fuel–aluminum powder (ALP), inorganic oxidizer–ammonium perchlorate (AP): NH_4ClO_4 , and other additives as plasticizers and burn rate modifiers, *etc.* ALP and AP are embedded into the polymer matrix of hydroxyl terminated polybutadiene (HTPB) and toluene di-isocyanate (TDI).^{1–7} The combustion of solid composite propellant releases chemical energy, which is converted into kinetic energy by means of the nozzle, and in turn it provides thrust to the solid rocket motor of a space vehicle or missile. The combustion efficiency of the SCP is a function of the stoichiometry of the propellant ingredients and strongly depends on the thermal decomposition of AP, as it is the major ingredient of SCP. The thermal decomposition of AP is greatly dependent on the composition (presence of any catalyst), particle size and shape of AP, which ultimately determine the burn rate of SCP. A higher burn rate with a lower pressure exponent is the desirable requirement; thus, thermal decomposition of AP is the key deciding factor to obtain the desired burn rate of SCP. The thermal decomposition of AP is greatly affected by the additives of transition metals, transition metal oxides and their mixtures. The decomposition mechanism has been understood by the concept of electron and proton exchange at elevated temperatures, as reported by Boldyrev *et al.* (2006).⁸ They studied the governing mechanism of the thermal decomposition of AP and proposed electron and proton transfer processes. AP is decomposed in two stages: low temperature decomposition, governed by the electron transfer process, and high temperature decomposition, initiated by the proton transfer process.⁹ The transition metals, transition metal oxides, and composites of ternary materials such as MnO_2 , CuO , NiO , CoFe_2O_4 , Fe_2O_4 , CuCr_2O_4 , *etc.* are common catalysts that are used to enhance the thermal decomposition of AP.^{9–20}

Recent developments in the area of carbon based materials such as carbon nanotubes (CNT), graphene oxide (GO) and reduced graphene oxide (rGO) have promised better catalysts and catalyst support due to their high specific surface area, high thermal and electrical conductivity. The dispersion difficulty of CNT leads to its restricted applications, whereas the hydrophilic nature of GO/rGO and the ease of synthesis provide the potential precursor material for the synthesis of graphene, which is a two dimensional sheet of carbon with the honeycomb structure that provides high specific surface area and superior electrical and thermal conductivity.^{21–23} The rGO has tremendous electron transfer properties. These properties of graphene have created remarkable scope for its potential applications in catalysis, particularly in the field of thermal decomposition of AP, promoted by the effect of the electron and proton transfer processes.

It is quite interesting to exploit both the catalytic properties of transition metal oxide based materials and graphene based materials in a single system. Recently, graphene based transition metal oxide composites (Fe_2O_3 , TiO_2 , Co_3O_4 and MnO_2 *etc.*) have been prepared and their effects on the thermal

decomposition of AP have been studied.^{24–29} Li *et al.* (2012) synthesized the Ni/graphene based nanocomposites using the simple one-pot method and observed the single step decomposition of AP.⁷ In 2013, the same group observed the negligible effect of pure graphene on the modification of the thermal decomposition of AP, whereas nanoparticles of Mn_3O_4 dispersed on GO showed tremendous effects.²⁵ Yuan *et al.* (2014) studied the thermal decomposition of AP in the presence of $\text{Fe}_2\text{O}_3/\text{GO}$ and the single step decomposition of AP at much lower temperatures, with high energy release against the individual effects of Fe_2O_3 and GO.²⁴

According to the literature, copper chromite ($\text{CuO}\cdot\text{CuCr}_2\text{O}_4$)^{18–20} and titanium oxide (TiO_2)^{21–23} are the most efficient metal oxide catalysts that considerably decrease the onset temperature of AP decomposition when they are used individually as additives in the AP. Despite the extensive and individual utilization of copper chromite and titanium oxide to manipulate the burn rate of AP, the physics and chemistry of their catalytic roles are not fully known. There is almost no literature on the combined effect of copper chromite and titanium oxide on the thermal decomposition of AP. Furthermore, the effect of rGO on the previously optimized Cu–Cr–O– TiO_2 system to enhance the burn rate of AP is a very interesting idea. We have recently reported, for the first time, the optimization of the concentration of TiO_2 in $\text{CuO}\cdot\text{CuCr}_2\text{O}_4$ to get the best composite ($\text{Cu}\text{--}\text{Cr}\text{--}\text{O}\text{--}0.7\text{TiO}_2$) for the improved thermal decomposition of AP.³¹ Herein, we investigate the effect of rGO in the Cu–Cr–O– 0.7TiO_2 system to enhance the thermal decomposition of AP as well as the burn rate of SCP. The aim of the present investigation is to achieve the highest burn rate of fuel at the minimum possible temperature. Efforts have been made to synthesize rGO and conduct rGO modification on ultrafine particles of $\text{CuCr}_2\text{O}_4\cdot 0.7\text{TiO}_2$ as synthesized by the sol–gel method. Several methods such as the hydrothermal method, ceramic method, co-precipitation, solid state, solution combustion method and sol–gel method have been reported to prepare the catalysts. However, due to having better control on the homogeneity, and the ease of preparation, the sol–gel method was employed.

2. Experimental

2.1 Sample preparation

2.1.1 Materials. The chemical reagents for the synthesis of graphene oxide and those used in the present study were of analytical grade and high (>99.9%) purity. The graphite rod was purchased from Graphite India Ltd., whereas, the other ingredients, *viz.* sulfuric acid (H_2SO_4), *ortho*-phosphoric acid (H_3PO_4), potassium permanganate (KMnO_4), hydrogen peroxide (H_2O_2), hydrochloric acid (HCl) and ethyl alcohol ($\text{C}_2\text{H}_5\text{OH}$) were purchased from Merck, Germany. Ammonium perchlorate (AP: NH_4ClO_4), with average particle size of 300 μm , was purchased from Pandian Chemicals Ltd., Cuddalore. Copper nitrate trihydrate ($\text{Cu}(\text{NO}_3)_2\cdot 3\text{H}_2\text{O}$) of extra pure grade was purchased from Titan Biotech Ltd., India, whereas chromium nitrate nonahydrate ($\text{Cr}(\text{NO}_3)_3\cdot 9\text{H}_2\text{O}$) was purchased from Central Drug House (P) Ltd., India. Anhydrous citric acid



(C₆H₈O₇) was purchased from Fisher Scientific, India. TiO₂ (P25) of nanometric size was purchased from Evonik Industries, Germany. All other reagents, except graphite powder, were used without further purification. The graphite in powder form was obtained by machining and grinding the as purchased graphite rod. The powder thus obtained was sieved and brought to the average particle size of 40 μm. The average particle size of ammonium perchlorate was reduced to 45 μm using an air classifying mill.

2.1.2 Methods

(a) *Synthesis of reduced graphene oxide (rGO)*. In order to get 1 g of rGO product, 120 ml of H₂SO₄ and 20 ml of H₃PO₄ were added to a beaker, with continuous stirring using magnetic stirrer. After 10 minutes of stirring, 1 g of graphite powder was dispersed into the beaker having a mixture of two different acids. The dispersion of the added graphite powder of average particle size of 40 μm was allowed a further 30 minutes of continuous stirring. The color of the mixture in the beaker was black due to graphite. After the homogeneous mixing of graphite particles, 3 g of KMnO₄ was added slowly to the beaker, which led to the color change of graphite added acids from black to greenish blue. In due time, the color change from greenish blue to pink was observed. Vigorous stirring of the obtained solution was allowed for a further 36 h at room temperature. The color of the solution became muddy yellow. Distilled water (100 ml) was then added to the obtained yellowish solution, followed by the addition of 30 ml of 30% v/v H₂O₂. An exothermic reaction was observed and finally, golden yellow particles were seen in the solution. The impurities were removed from the solution by washing with water, followed by 30% v/v of HCl and C₂H₅OH. The solid particles were removed from the solution by centrifuging it at 5000 rpm. The obtained solid particles were dried in the oven at 60 °C for 6 h to get GO, which was transformed into rGO by a thermal treatment method as reported in literature.³⁰ Finally, rGO was calcined at 1050 °C to improve its activity by reducing the attached functional groups. The rGO thus obtained was ready for further use.

(b) *Synthesis of the Cu–Cr–O–0.7TiO₂ composite*. Tri-metallic oxide (Cu–Cr–O–0.7TiO₂) was prepared using the sol–gel method. The molar ratio of Cu/Cr was kept at 0.7 and very interestingly, the molar concentration of TiO₂, also 0.7 mol%, was found to be best among the three concentrations (0.5, 0.7 and 0.9 mol%) of TiO₂ according to our previous study.³¹ The synthesis procedure for Cu–Cr–O–0.7TiO₂ followed in the present investigation is exactly the same as in our previous report.³¹ Among the six compositions of tri-metallic oxide with three varying concentrations (0.5, 0.7 and 0.9 mol%) of TiO₂ calcined at two different temperatures, 300 and 1050 °C, the Cu–Cr–O–0.7TiO₂ composite calcined at 300 °C was found to be the best catalyst, which remarkably enhanced the burn rate of AP. The AP with particle size of 45 μm (AP_{45 μm}) exhibited better thermal decomposition behavior than the AP having particle size of 300 μm (AP_{300 μm}) as reported in literature (revealed in our previous work);³¹ therefore, we used AP_{45 μm} in our present study and it is represented as AP. When 0.7 mol% of TiO₂ added Cu–Cr–O composite, calcined at 300 °C, was used as the catalyst in AP, a very sharp single step decomposition of AP_{45 μm} at 306 °C

was obtained, which was 79 °C lower than that of pure AP. Since the catalyst sample Cu–Cr–O–0.7TiO₂, calcined at 300 °C, had achieved remarkable enhancement in the thermal decomposition of AP when used as modifier in pure AP, the further modification by rGO in this composition may offer more significant results.

(c) *Synthesis of Cu–Cr–O–0.7TiO₂–rGO*. In order to synthesize the rGO incorporated Cu–Cr–O–0.7TiO₂ composite, 10 wt% of rGO was added to 90 wt% of Cu–Cr–O–0.7TiO₂. Already synthesized rGO (10 g) was poured into 400 ml ethanol in a beaker. The rGO suspension was subjected to a magnetic stirrer for continuous stirring, and the Cu–Cr–O–0.7TiO₂ powder was then added slowly to this suspension. The rGO modified Cu–Cr–O–0.7TiO₂ mixture was continuously stirred at 80 °C until a paste-like material was obtained. The paste was dried in an oven at 130 °C for 3 h. The material thus obtained was then crushed using a mortar and pestle to get a homogeneous fine powder of Cu–Cr–O–0.7TiO₂–rGO. This powder was further calcined at 300 °C for 4 h in the N₂ atmosphere to form the desired Cu–Cr–O–0.7TiO₂ composite materials having excellent catalytic properties on thermal decomposition of AP.

2.2 Sample characterization

The powder X-ray diffraction method was employed to record the diffraction pattern of the synthesized catalyst using an advanced X-ray diffractometer (Rigaku Miniflex II, Desktop X-ray D) with CuK_α radiation (λ = 1.5418 Å) with Ni filter at a scanning speed of 3° min⁻¹ and scanning range of 20–80°, operated at 30 kV and 15 mA. The surface morphology and particle size analyses were carried out using scanning electron microscopy (SEM) operated at 10 kV (ZEISS EVO 18). Elemental analysis of synthesized powder was carried out *via* the energy dispersive X-ray analysis method, using the INCA 250 EDS instrument with X-max of 20 mm detector, coupled with SEM (ZEISS EVO 18). Fourier Transform Infrared (FTIR) spectroscopy analysis was performed at room temperature using an FTIR spectrometer (Perkin Elmer with model no. 577 FT-IR). The FT-IR spectrum was recorded in the wavenumber range 4000–400 cm⁻¹ using the KBr pellet method. The Raman spectrum of the GO sample was recorded using a Raman spectrometer (Renishaw, UK) with an excitation source of 514.5 nm wavelength. To confirm the formation of GO, the presence of D and G bands is mandatory in the Raman spectrum. The oxidation state and elemental analysis of the samples were determined using X-ray photon spectroscopy (XPS-model PHI5000, Versa Probe II, physical Electronics) with AlK_α radiation for monochromatic X-ray of energy E = 1486.6 eV, Ar ion gun sputtering, beam diameter of 10 μm, 6–25 W and 15 kV, surface clean sputtering 2 kV, 2 mm × 2 mm for 1 min. The XPS patterns of various compositions were taken at 187.5 eV pass energy for the detection of all possible elements with atomic concentration limit above 0.5%. To confirm the oxidation states of constituent elements, the core level analysis was done at 11.75 eV pass energy at a step size of 0.1 eV with X-ray rating of 100 micron in diameter, 25 W and 15 kV. The electron neutralizer and Ar ion gun were used during the experiment for charge loss compensation, which occurred during the XPS process. The



core level spectra were recorded under ultra-high vacuum (UHV) conditions of about 10^{-10} Torr. The adventitious carbon was recorded for reference from the surface and then sputtered by Ar ion gun at a rating of 2 kV, 2×2 at a sputter rate of 10 nm min^{-1} of SiO_2 standard. Thermogravimetric and differential thermogravimetric analysis (TG-DTA) curves were obtained with LAB-SYSTEM Setaram Instrumentation (Serial no. 1-3347-1 DTA/TGA/DSC) in nitrogen atmosphere at a heating rate of $10 \text{ }^\circ\text{C min}^{-1}$. Thermal decomposition of AP and modified AP was determined using DTA curves.

2.3 Catalytic activity measurements

The catalytic activity of the as synthesized composite materials was determined over the thermal decomposition of AP. In order to analyze the catalytic efficiency of the materials, the measured parameters were the burn rate of the solid composite propellant, the temperature of crystallographic change, low temperature decomposition and high temperature decomposition. A known quantity of AP ($\text{AP}_{45 \mu\text{m}}$) powder was mixed with varying amounts (2.5, 5.0, 7.5 and 10 wt%) of synthesized catalyst (Cu-Cr-Ti-O-rGO). These samples were prepared homogeneously (by the ball mill method) to see the effect of the synthesized catalyst on the burn rate of AP. The resultant compositions were analyzed by thermogravimetric and differential thermal (TG-DTA) characterizations at the heating rate of $10 \text{ }^\circ\text{C min}^{-1}$ in a N_2 environment. Nichrome wire was used to supply the 24 volt of power supply, and the produced noise signal was captured through the acoustic measurement sensor. The burn rate of the SCP was achieved using the strand burner, and testing was conducted at 33 bar in water.

3. Results and discussion

3.1 X-ray diffraction (XRD) pattern of synthesized catalyst

The crystalline phase and phase identification were carried out using the XRD pattern of the Cu-Cr-O-0.7TiO₂-rGO composition as shown in Fig. 1. The characteristic diffraction peak for

rGO with (002) as (*hkl*) values appears at the diffraction angle (2θ) of 26.1° , matching the JCPDS File no. 03-0401.^{32,33} The interlayer distance (*d*-spacing) between two layers is about 0.33 nm. The strongest diffraction peak at 43.02° is due to copper chromite CuCr_2O_4 , corresponding to the (400) plane (see the JCPDS File no. 26-0509). However, a weak peak at 30.02° in the pattern is due to the (220) plane of the CuCr_2O_4 copper chromite.

Secondary phase of copper chromite, *i.e.* $\text{Cu}_2\text{Cr}_2\text{O}_4$, was also identified by the presence of the diffraction peaks at 36.98° and 62.30° , corresponding to planes (100) and (*hkl*) respectively, matching the JCPDS File no. 05-0668.

Diffraction peaks due to Cu_2O appeared at 35.48° , 38.82° and 75.23° , corresponding to (111), (110) and (220), respectively, as (*hkl*) values indexed to JCPDS File no. 80-4746. Titanium oxide was observed in two phases, *i.e.* Ti_2O_3 (JCPDS File no. 89-4746) and TiO_2 (JCPDS File no. 89-4203) at the diffraction angles of 40.54° and 78.94° , with corresponding planes (113) and (117), respectively. The crystallite size of the synthesized catalyst was calculated by full width at half maximum (FWHM), using the Scherrer formula as given below in eqn (i).

$$d = \frac{0.9\lambda}{\beta \cos \theta} \quad (\text{i})$$

d = crystallite size in nm, λ = wavelength in nm, β = full width at half maximum and θ = half of Bragg's angle. The crystallite size of the sample was observed to be 32 nm.

3.2 Infrared spectroscopy of synthesized catalyst

The IR spectrum of the Cu-Cr-O-0.7TiO₂-rGO catalyst sample is shown in Fig. 2. The strongest absorption envelope at 3430 cm^{-1} is assigned to the symmetric stretching mode of OH^- .^{34,35} Another strong shoulder observed at wavenumber 1641 cm^{-1} is due the C=C, which is the characteristic shoulder of rGO. The position of this band may vary depending on the host molecule to which H_2O is attached. The medium intensity bands recorded at 2926 and 2861 cm^{-1} are attributed to the stretching



Fig. 1 XRD pattern of the synthesized catalyst.

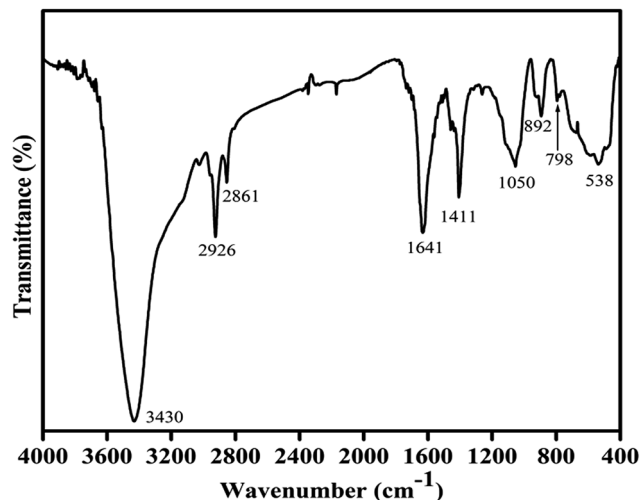


Fig. 2 FT-IR pattern of the synthesized catalyst.



vibrations of $\nu(\text{C-H})$ of citric acid. A medium and sharp shoulder appearing at 1411 cm^{-1} may be assigned to the symmetric vibrations of surface hydroxyl groups. However, this band may also be attributed to ν_3 carbonate ions (CO_3^{2-}). An un-indexed weak shoulder appearing at 1278 cm^{-1} is attributed to the coupled bending and stretching vibrations of COO^- of citric acid. Notably, citric acid has its melting point at $310\text{ }^\circ\text{C}$, which is just above $300\text{ }^\circ\text{C}$; this is the reason why citric acid is not destroyed at $300\text{ }^\circ\text{C}$.³¹ The shoulder at 1050 cm^{-1} can be assigned to the bending vibrations of C-H of citric acid. The weak absorption bands observed at 892 , 798 and 697 cm^{-1} are attributed to the different vibrational modes of TiO_2 ,³¹ which exhibit strong absorption in the range $600\text{--}890\text{ cm}^{-1}$ when treated with some other metal ions, as in the present case. A broad absorption band centered at 538 cm^{-1} is assigned to the characteristic vibrational band (asymmetric) of Cu-O in CuO; it also contains stretching bands of Cu-O-Cr.³¹

3.3 Raman spectroscopy of the synthesized catalyst

Fig. 3 shows the room temperature Raman spectrum of the synthesized composites of Cu-Cr-Ti-O/rGO. To avoid the decomposition of the sample, a laser of low power (5 mW) was employed for recording the Raman spectrum. The spectrum was recorded in the wavenumber range of 3000 to 300 cm^{-1} . The two most intense features of the Raman spectrum of rGO are the presence of a G band and D bands. The G band is observed at $\sim 1580\text{ cm}^{-1}$, and this band always appears as the strongest band in the Raman spectrum, as is clearly shown in Fig. 4.^{36,37} Another significant mark of the Raman profile of rGO is the 2D band appearing at $\sim 2700\text{ cm}^{-1}$, as usually observed in graphitic structures. The zone-boundary phonons violate the Raman fundamental selection rule and consequently give rise to a peak at $\sim 1352\text{ cm}^{-1}$ in defective graphite, called the D-band, rather than the appearance of a Raman peak in the first order Raman spectrum of defect-free graphite.^{36,38,39} The Raman spectrum of the graphene has a single sharp 2D peak; the number of layers in graphene is estimated based on the



Fig. 3 Raman spectrum of the synthesized catalyst.



Fig. 4 SEM images of the synthesized catalyst at (a) $1\text{ }\mu\text{m}$ and (b) $2\text{ }\mu\text{m}$ magnifications.

intensity of the 2D peak. Literature shows that as the number of layers of graphene sheets increases, the intensity of the G band increases significantly, whereas the intensity of the 2D band decreases.^{36,39-41}

The position of the D band in the present spectrum is exactly at 1352 cm^{-1} . The G and D bands appear due to the doubly degenerate zone centre E_{2g} mode at $\sim 1580\text{ cm}^{-1}$ and the breathing modes of six atom rings at 1352 cm^{-1} because of the defects in graphite. The recorded Raman profile containing the conventional and characteristic G, D and 2D bands at their defined positions with defined intensity confirm the presence of graphene oxide in the prepared catalyst composite.

3.4 Scanning electron microscopy (SEM) and associated energy dispersive X-ray (EDX) analysis of the synthesized catalyst

The surface morphology of the synthesized catalyst sample is shown in Fig. 4(a and b). The microstructures of the sample at different magnifications (a) $2\text{ }\mu\text{m}$ and (b) $1\text{ }\mu\text{m}$ were determined using scanning electron microscopy, operated at 10 kV . The micrographs show that the particles are spherical in shape, and the particle size is in the range of $200\text{--}300\text{ nm}$. Elemental compositions of the rGO added Cu-Cr-O-TiO₂ catalyst sample were determined using EDX, and the observed atomic wt% of the constituent elements is shown in Table 1. This analysis confirmed the presence of carbon, copper, chromium, titanium and oxygen. The increasing weight% of oxygen with an increase in the temperature may occur due to the transformation of the intermediate compounds of Cu-Cr-O-citric acid into metal oxides. Interestingly, CuO already showed its presence in XRD patterns of the samples calcined at $1050\text{ }^\circ\text{C}$, but not in the samples calcined at $300\text{ }^\circ\text{C}$.

Table 1 Elemental composition of the synthesized catalyst

Element	Weight%
C	38.33
O	13.21
Ti	26.13
Cr	13.89
Cu	8.44



3.5 Transmission electron microscopy (TEM) of the synthesized catalyst

Fig. 5 shows the transmission electron microscopic images of the Cu–Cr–O–0.7TiO₂–rGO composite sample calcined at 300 °C. Two images of the composite at two different magnifications (a) 200 nm and (b) 20 nm are shown; however, the inset image (c) represents the selected area diffraction pattern (SAED) pattern. At first glance, in image (a), the Cu–Cr–O–0.7TiO₂ particles of size around 100 nm can be seen easily in yellow dotted yellow rings as shown by yellow arrows and rest is rGO as shown by bright brown arrows. More clear view of rGO sheets is captured at higher magnification as shown in image (b). The Cu–Cr–O–0.7TiO₂ particles are scattered on the rGO sheets to form an organic–inorganic blend.

3.6 X-ray photoelectron spectroscopy (XPS)

The surface composition and oxidation states of the constituent elements of synthesized catalyst were represented by the characteristic core level spectra of Cu, Cr, Ti, O and C. The XPS pattern of Cu is shown below in Fig. 6.

Copper is observed in two oxidation states namely Cu⁺ and Cu²⁺ in 72.24% and 27.76%, respectively. The XPS spectrum of

Cu²⁺ is characterized by two spin orbit doublets with strong satellite peaks. The binding energies for Cu 2p_{3/2} and Cu 2p_{1/2} are 933.5 eV and 953.5 eV, respectively. Three satellite peaks with binding energies, 941.5 eV, 944.03 eV and 962 eV support the presence of CuO, or mixed oxides CuO and Cu₂O. The low energy component with Cu 2p_{3/2} at 933.8 eV is associated with Cu²⁺ in octahedron sites, whereas the high energy component at 935.3 eV is assigned to Cu²⁺ in tetrahedral sites.

The XPS profile of Cr is shown in Fig. 7. The XPS profile shows three peaks, two of which appear with binding energies of 586.4 eV and 576.07 eV, corresponding to Cr 2p_{1/2} and Cr 2p_{3/2}.⁴² The third peak with binding energy of 568.98 eV could not be assigned. The XPS profile of TiO₂ is represented in Fig. 8. Titanium is observed in two different oxidation states, *i.e.*, Ti²⁺ and Ti⁴⁺ in 1.68% and 77.7%, respectively. TiO₂ exhibits two peaks having binding energies of 458.5 eV and 464.05 eV, attributed to TiO₂ 2p_{3/2} and TiO₂ 2p_{1/2}. Fig. 9 exhibits the XPS pattern of oxygen (O). Oxygen shows a peak with binding energy 530.16 eV, which is assigned to O 1s. This peak is the main oxygen peak, ascribed to the lattice oxygen in TiO₂.



Fig. 5 TEM images of synthesized catalyst at two different magnifications (a) 200 nm and (b) 20 nm; (c) SAED pattern as inset image.



Fig. 6 XPS Pattern of copper with fitted curves.



Fig. 7 XPS Pattern of chromium with fitted curves.

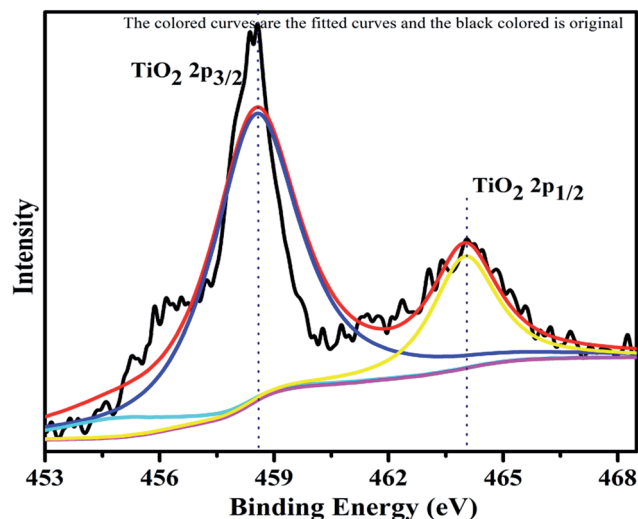


Fig. 8 XPS Pattern of titanium dioxide with fitted curves.



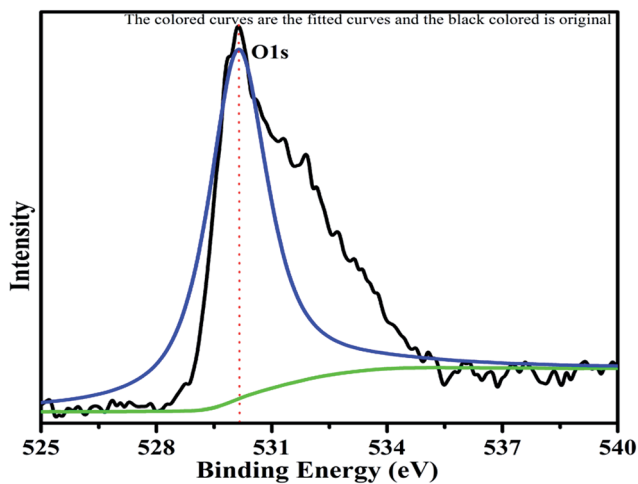


Fig. 9 XPS pattern of oxygen with fitted curves.

The XPS spectrum of carbon is shown in Fig. 10. The C 1s peak with binding energy of 284.4 eV can be clearly seen in the pattern. This is the carbon of rGO used as additive in the catalyst. This C 1s spectrum is taken as the reference standard for the peak shift correction of other elements because of the peak at 284.4 eV serves as the reference for the C–C bond. The carbon was observed as an asymmetric single bonded carbon (C–C) with sp^2 hybridization, the characteristic state of graphene. The XPS study also confirmed the presence of rGO, due to the maximum intensity peak at 284.4 eV (see Fig. 10), which is associated with the asymmetric single bond of sp^2 hybridization of carbon.^{43,44}

3.7 Catalytic efficiency

3.7.1 The effect of the synthesized catalyst on the thermal decomposition of ammonium perchlorate (AP). The catalytic activity of the as-synthesized material was carried out by the thermogravimetric and differential thermal analysis (TG-DTA) technique. The DTA curve of pure AP is shown in Fig. 11.³⁰

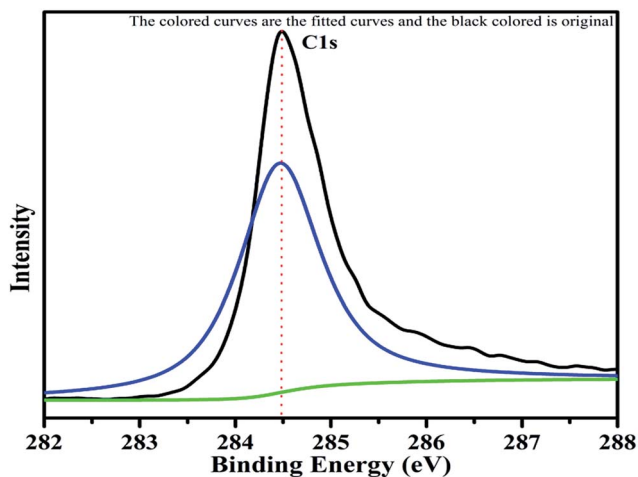


Fig. 10 XPS pattern of carbon with fitted curves.




Fig. 11 DTA curve of pure ammonium perchlorate (AP).

According to the curve, pure AP exhibits the first endothermic peak at the temperature of 253 °C, associated with the crystallographic change of AP from orthorhombic to cubic. This is the characteristic crystallographic conversion of the AP^{30} , which exists in the orthorhombic structure up to 230 °C, beyond which it gets transformed into the cubic structure. The cubic structure of AP provides a comparatively dense packing and crystal defects resulting in the faster rate of thermal decomposition and in turn, releases high energy during the decomposition process.^{45–49} The first exothermic peak or low temperature decomposition (LTD) peak is observed at 301 °C. LTD is assigned to the formation of intermediates, *i.e.*, the decomposition of AP into NH_4^+ and ClO_4^- , which consequently form ammonia (NH_3) and perchloric acid ($HClO_4$), respectively. The low temperature decomposition is governed by the electron transfer process. This decomposition is due to dissociation and sublimation and may be more magnified in the reaction eqn (ii):




The critical and most important factor governing the decomposition of (NH_4ClO_4) is the above-mentioned electron transfer process. The systematic scheme is given as follows:



ClO_3 acts as an electron scavenger and is converted into ClO_3^- .




The tri-metal composite of Cu–Cr–Ti–O (*i.e.* Cu–Cr–O–0.7TiO₂) exhibits excellent properties, due the following proposed mechanism. Cu–Cr–O heterogeneously couples with TiO₂, due to the suitable energy band gap. Cu–Cr–O has a 3d orbital structure and can simultaneously participate in the process of electron transfer. Cu–Cr–O releases the electron under stimulated conditions and it induces the conduction band of TiO₂ resulting in the active participation of both Cu–Cr–O and TiO₂. The mechanism of electron release is as follows:



However, in the case of the Cu–Cr–O–TiO₂–rGO composite, rGO exhibits excellent electrical and optoelectrical properties with n-type semiconducting nature,⁵⁰ which allows it to accept the electrons released from ClO₄[−], and intermediates are formed during the decomposition of ammonium perchlorate (NH₄ClO₄). A continuous electron transfer process from metal oxides and ClO₄[−] takes place. In the Cu–Cr–O–TiO₂–rGO system, the Cu–Cr–O–TiO₂ being the p-type semiconductor releases the electron and rGO being the n-type semiconducting material accepts and facilitates the motion of those electrons released from Cu–Cr–O–TiO₂ more smoothly. Consequently, the electron transfer process was tremendously enhanced, due to having high electron mobility, compared to the Cu–Cr–O–TiO₂ system.

The second exothermic peak (or third *i.e.* final decomposition) of AP occurred at the comparatively higher temperature of 391 °C. This is known as the high temperature decomposition (HTD) peak. HTD behavior is also exothermic in nature like LTD. HTD peak at 391 °C is associated with the further decomposition of H₂O, HCl, N₂, H₂ and O.⁵¹ At high temperature decomposition, HClO₄ gets converted into small molecules, and the reaction is governed by photon transfer process. The probable reactions are shown below in eqn (iii) and (iv).



The particles of CuCr₂O₄·0.7TiO₂ reduced the peak temperature of high decomposition with the merging of the low temperature decomposition peak at a faster rate. CuCr₂O₄·0.7TiO₂ initiated the decomposition process by the electron transfer process, followed by the deprotonation of HClO₄ on a solid surface in the gaseous phase. During the decomposition, rGO plays a vital role in accelerating the electron transfer process.

DTA curves of AP modified with different amounts (2.5, 5.0, 7.5 and 10 wt%) of synthesized catalyst (Cu–Cr–O–TiO₂–GO) are shown in Fig. 12, 13, 14 and 15, respectively. A careful



Fig. 12 DTA curve of AP modified with 2.5 wt% of catalyst.

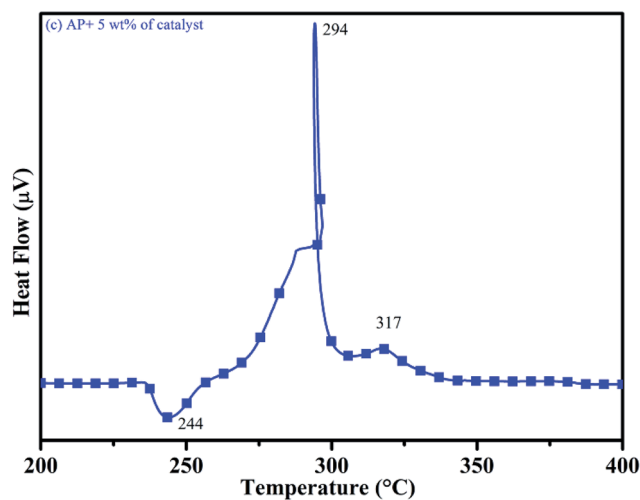


Fig. 13 DTA curve of AP modified with 5.0 wt% of catalyst.

examination of the first endothermic peaks in the DTA curves of all the samples, *i.e.* pure as well as modified AP, concluded that the incorporation of catalyst additive into pure AP significantly reduced the crystallographic transition temperature from 253 °C to 242 °C. However, the study of this peak does not fall within the scope of the present study, yet the results are discussed briefly; however, another two exothermic peaks, LTD and HTD, are of interest in the present study. A significant effect of different wt% of synthesized catalyst in pure AP has been observed on the low as well as high temperature decomposition peak positions of AP. In the AP sample modified with the least amount (2.5 wt%) of catalyst (see Fig. 12), the partial decomposition occurred at 286 °C rather than 301 °C, and complete decomposition took place at 341 °C rather than 391 °C as for pure AP. Peak positions of LTD and HTD were reduced significantly by 15 °C and 50 °C, respectively, compared to the those of pure AP. On the other hand, the separation between LTD and HTD was also reduced. More interesting results were observed when the amount of catalyst was increased. As the 5 wt% of the





Fig. 14 DTA curve of AP modified with 7.5 wt% of catalyst.

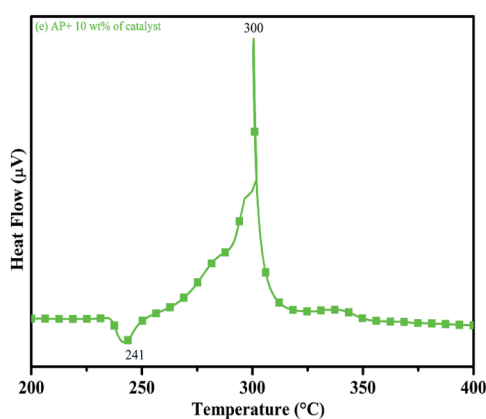


Fig. 15 DTA curve of AP modified with 10 wt% catalyst.

synthesized catalyst was added into pure AP, interestingly, both the LTD and HTD merged, followed by single peak decomposition at 294 °C as shown in Fig. 13. A tremendous lower shift of 97 °C of HTD and 7 °C lower shift of LTD were noticed. The single stage decomposition of AP assisted by the catalyst shows the spontaneous process of decomposition occurring within an exceptionally lower time interval. This graph contains a very small hump at 317 °C, which may have appeared due to an infinitesimally small amount of NH_4ClO_4 or HClO_4 left in the sample. When the amount of catalyst was further increased to 7.5 wt% and 10 wt% in AP, the recorded thermal decomposition profiles of AP showed single decomposition peaks at 303 °C (see Fig. 14) and 300 °C (see Fig. 15), respectively. Single stage peak decomposition positions for higher concentrations of catalyst are shifted towards higher comparatively temperatures, which is against one of our requirements, since our objective is to reduce the thermal decomposition of AP with single stage decomposition. The addition of larger amounts (7.5 wt% and 10 wt%) of catalyst does not have a significant impact on the thermal decomposition of AP, compared to the addition of 5 wt% of catalyst into AP. However, these samples (7.5 and 10

wt% of catalyst into AP) have much better performance than the industrial catalyst (ACR) as well as the previously reported catalysts.³¹

Thus, excellent single stage decomposition of AP was achieved at minimum temperature (294 °C), with maximum decomposition rate (burn rate) in the presence of 5.0 wt% of synthesized catalyst material in AP. Fig. 16(a–e) represents the TGA curves of (a) pure AP and AP with (b) 2.5, (c) 5, (d) 7 and (e) 10 wt% of synthesized catalyst ($\text{Cu-Cr-O-TiO}_2\text{-GO}$) recorded in the temperature range of 200–500 °C. TGA curves of all the samples are in line with the corresponding DTA curve. TGA curves show the change in % weight loss of the sample in the temperature range of 260 to 380 °C. Beyond 380 °C, the TGA curve becomes straight, which clearly explains the completion of the thermal decomposition of ammonium perchlorate.

3.8 Burn rate of solid composite propellant

3.8.1 Effect of the synthesized catalyst (modified AP) on the burn rate of solid composite propellant (SCP). The combustion efficiency of the SCP is the function of the stoichiometry of the propellant ingredients. Since the major ingredient (68 wt%) of SCP is AP, the thermal decomposition of AP is the major deciding factor for the combustion efficiency of SCP. Furthermore, the thermal decomposition of AP is strongly dependent on its composition, particularly on the presence of catalyst, as well as on particle size and the shape of AP. A change in the thermal decomposition of AP will ultimately affect the burn rate of SCP. The better the thermal decomposition of AP, the higher the burn rate of SCP. In this study, the thermal decomposition of AP was remarkably enhanced using different concentrations of synthesized catalyst in AP. The AP modified by the synthesized catalyst is used in SCP to enhance the burn rate of SCP. The efficiency of the synthesized catalyst in terms of the burn rate of SCP is comparable to that of the industrial catalyst (ACR). The higher burn rate at low temperature with the lower pressure exponent is our requirement. The burn rate of the SCP is evaluated at combustion pressure of 33 bar using the acoustic



Fig. 16 (a–e): TGA curves of (a) pure AP, and AP with (b) 2.5, (c) 5, (d) 7 and (e) 10 wt% of the catalyst.



- 5 D. L. Reid, A. E. Russo, R. V. Caro, M. A. Stephens, A. R. LePage, T. C. Spalding, E. L. Petersen and S. Seal, *Nano Lett.*, 2007, 7, 2157–2161.
- 6 M. A. Stephens, E. L. Petersen, R. Carro, D. L. Reid and S. Seal, *Propellants, Explos., Pyrotech.*, 2010, 35, 143–152.
- 7 N. Li, M. Cao, Q. Wu and C. Hu, *CrystEngComm*, 2012, 14, 428–434.
- 8 V. V. Boldyrev, *Thermochim. Acta*, 2006, 443, 1–36.
- 9 P. R. Patil, V. N. Krishnamurthy and S. S. Joshi, *Propellants, Explos., Pyrotech.*, 2008, 33, 266–270.
- 10 V. G. Dedgaonkar and D. B. Sarwade, *J. Therm. Anal.*, 1990, 36, 223–229.
- 11 K. Kishore and M. R. Sunitha, *AIAA Pap.*, 1979, 17, 1118–1125.
- 12 L. Liu, F. Li, L. Tan, L. Ming and Y. Yi, *Propellants, Explos., Pyrotech.*, 2004, 29(1), 34–38.
- 13 L. Song, S. Zhang, B. Chen, J. Ge and X. Jia, *Colloids Surf., A*, 2010, 360, 1–5.
- 14 E. A. Gheshlaghi, B. Shaabani, A. Khodayari, Y. A. Kalandaraghand and R. Rahimi, *Powder Technol.*, 2012, 217, 330–339.
- 15 Y. Zhnag, X. Liu, J. Nie, L. Yu, Y. Zhong and C. Huang, *J. Solid State Chem.*, 2011, 184, 387–390.
- 16 H. Xu, X. Wang and L. Zhang, *Powder Technol.*, 2008, 185, 176–180.
- 17 R. A. Chandru, S. Patra, C. Oommen, N. Munichandraiah and B. N. Raghunandan, *J. Mater. Chem.*, 2012, 22(14), 6536–6538.
- 18 T. Liu, L. Wang and B. Hu, *Mater. Lett.*, 2008, 62, 4056–4058.
- 19 S. Zhao and D. Ma, *J. Nanomater.*, 2010, 2010, 1–5.
- 20 L. Chen, P. Li and G. Li, *J. Alloys Compd.*, 2008, 464, 532–536.
- 21 W. S. Hummers and R. E. Offeman, *J. Am. Chem. Soc.*, 1958, 80(6), 1339.
- 22 S. Pei and H. M. Cheng, *Carbon*, 2012, 50(9), 3210–3228.
- 23 S. Park and R. S. Ruoff, *Nat. Nanotechnol.*, 2009, 4(4), 217–224.
- 24 Y. Yuan, W. Jiang, Y. Wang, P. Shen, F. Li, P. Li, F. Zhao and H. Gao, *Appl. Surf. Sci.*, 2014, 303, 354–359.
- 25 N. Li, Z. Geng, M. Cao, L. Ren, X. Zhao, B. Liu, Y. Tian and C. Hu, *Carbon*, 2013, 54, 124–132.
- 26 Z. B. Lei, F. H. Shi and L. Lu, *ACS Appl. Mater. Interfaces*, 2012, 4(2), 1058–1064.
- 27 P. Wang, Y. M. Zhai, D. J. Wang and S. J. Dong, *Nanoscale*, 2011, 3(4), 1640.
- 28 W. Zhang, Q. Luo, X. Duan, Y. Zhou and C. Pei, *Mater. Res. Bull.*, 2014, 50, 73–78.
- 29 X. Guan, L. Li, J. Zheng and G. Li, *RSC Adv.*, 2011, 1, 1808–1814.
- 30 D. Zhan, Z. Ni, W. Chen, L. Sun, Z. Luo, L. Lai, T. Yu, A. Thye, S. Wee and Z. Shen, *Carbon*, 2011, 49, 1362–1366.
- 31 H. Kumar, P. N. Tengli, V. K. Mishra, P. Tripathi, D. B. Pal and P. K. Mishra, *RSC Adv.*, 2017, 7, 12486–12495.
- 32 H. K. Jeong, Y. P. Lee, M. H. Park, K. H. An, I. J. Kim, *et al.*, *J. Am. Chem. Soc.*, 2008, 130, 1362.
- 33 F. Yang, M. Zhao, B. Zheng, D. Xiao, L. Wu and Y. Guo, *J. Mater. Chem.*, 2012, 22, 25471–25479.
- 34 V. K. Mishra, B. N. Bhattacharjee, D. Kumar, S. B. Rai and O. Parkash, *New J. Chem.*, 2016, 40, 5432–5441.
- 35 V. K. Mishra, S. B. Rai, B. P. Asthana, O. Parkash and D. Kumar, *Ceram. Int.*, 2014, 40, 11319–11328.
- 36 A. Kaniyoor and S. Ramaprabhu, *AIP Adv.*, 2012, 22, 032183.
- 37 K. N. Kudin, B. Ozbas, H. C. Schniepp, R. K. Prud'homme, I. A. Aksay and R. Car, *Nano Lett.*, 2008, 8(1), 36–41.
- 38 R. J. Nemanich and S. A. Solin, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1979, 20, 392.
- 39 A. C. Ferrari, J. C. Meyer, V. Scardaci, C. Casiraghi, M. Lazzeri, F. Mauri, S. Piscanec, D. Jiang, K. S. Novoselov, S. Roth and A. K. Geim, *Phys. Rev. Lett.*, 2006, 97, 187401.
- 40 A. Das, B. Chakraborty and A. K. Sood, *Bull. Mater. Sci.*, 2008, 31, 579.
- 41 L. G. Cancado, K. Takai, T. Enoki, M. Endo, Y. A. Kim, H. Mizusaki, N. L. Speziali, A. Jorio and M. A. Pimenta, *Carbon*, 2008, 46, 272.
- 42 M. Aronniemi, J. Sainio and J. Lahtinen, *Surf. Sci.*, 2005, 578, 108–123.
- 43 A. H. C. Neto, F. Guinea, N. M. R. Peres, K. S. Novoselov and A. K. Geim, *Rev. Mod. Phys.*, 2009, 81, 109–163.
- 44 D. S. Sutar, G. Singh and V. Divakar Botcha, *Appl. Phys. Lett.*, 2012, 101, 103103–103107.
- 45 G. P. Sutton and O. Biblorge, *Rocket Propulsion Elements*, A Wiley Inter-Science Publication, New York, 7th edn, 2000.
- 46 P. W. M. Jacob and H. M. Whitehead, *Chem. Rev.*, 1969, 69, 551–590.
- 47 P. Wang, Y. M. Zhai, D. J. Wang and S. J. Dong, *Nanoscale*, 2011, 3(4), 164011.
- 48 C. Ping, F. Li, Z. Jian and J. Wei, *Propellants, Explos., Pyrotech.*, 2006, 31, 452–455.
- 49 W. Zhang, P. Li, H. Xu, R. Sun, P. Qing and Y. Zhang, *J. Hazard. Mater.*, 2014, 268, 273–280.
- 50 G. Giovannetti, P. A. Khomyakov, G. Brocks, V. M. Karpan, J. van den Brink and P. J. Kelly, *Phys. Rev. Lett.*, 2008, 101, 026803.
- 51 A. G. Keenan and R. F. Q. Siegmund, *Chem. Soc. Rev.*, 1969, 23, 430–452.

