



Cite this: *J. Mater. Chem. A*, 2022, **10**, 6153

Inducing atomically dispersed $\text{Cl}-\text{FeN}_4$ sites for ORRs in the SiO_2 -mediated synthesis of highly mesoporous N-enriched C-networks†

Xiong Zhang,^a Lai Truong-Phuoc,^a Xuemei Liao,^{*ab} Vasiliki Papaefthimiou,^a Matteo Pugliesi,^c Giulia Tuci,^c Giuliano Giambastiani,^c  Sergey Pronkin^{*a} and Cuong Pham-Huu^{*a}

Atomically dispersed iron sites within N-enriched C-networks are promising low-cost catalytic materials for electrochemical applications. At odds with their often-outstanding performance in challenging electrocatalytic processes (*i.e.* oxygen reduction reaction, ORR) their fabrication strategy frequently relies on trial-and-error approaches. Moreover, the complex chemical nature of these hybrids is often dictated by the use of highly aggressive etching/doping thermo-chemical treatments. Therefore, the development of simplified chemical protocols based on cheap and abundant raw materials ensuring highly reproducible synthetic paths with the prevalent generation of discrete single-atom sites in a definite coordination environment remains a challenging issue to be properly addressed. In this contribution, the synthesis of hierarchically porous and N-enriched C-networks prevalently containing $\text{Cl}-\text{FeN}_4$ sites is proposed. The outlined procedure takes advantage of citrate ions as carriers for N-sites and a sacrificial C-source for the synthesis of N/C matrices. At the same time, the chelating character of citrate polyions fosters the complexation of transition metals for their ultimate atomic dispersion in C/N matrices. The procedure is finally adapted to the use of common inorganic hard templates and porogens for the control of the material morphology. Avoiding any thermo-chemical etching/doping phase, the as-prepared catalytic material has shown remarkably high ORR performance in an alkaline environment. With a half-wave potential ($E_{1/2}$) of 0.88 V, a kinetic current density up to 109.6 A g^{-1} (normalized to the catalyst loading at 0.8 V vs. RHE) and outstanding stability, it largely outperforms commercial Pt/C catalysts and certainly ranks among the most performing ORR Fe-single-atom-catalysts (Fe-SACs) reported so far.

Received 5th November 2021
Accepted 20th November 2021

DOI: 10.1039/d1ta09519f
rsc.li/materials-a

1. Introduction

The kinetically sluggish oxygen reduction reaction (ORR) is certainly among the electrochemical processes that gained steadily growing interest during the last few years from the catalysis and material chemistry community. It represents the central core of many energy-related transformations, and its tight dependence on the use of noble metal-based catalysts has seriously hampered any large-scale implementation and

commercialization of energy storage and conversion devices such as fuel cells and metal-air batteries.^{1,2} The rate of the ORR at a cathodic compartment of an electrochemical cell can be several orders lower than that of the semi-reaction occurring at the anodic counterpart (*i.e.* hydrogen oxidation reaction – HOR) and their ultimate performance depends on the use of Pt or platinum group metal (PGM) alloys as electrocatalysts.^{3,4} The limited natural abundance of Pt and PGMs, their relatively high costs and moderate tolerance to alcohol (*i.e.* MeOH in alcohol cross-over phenomena) or gas impurities (*i.e.* CO) have extensively stimulated fundamental research towards alternative, costless and definitively more sustainable catalytic systems for the ORR process to occur.^{5–10} Earth-abundant, transition metal (TM)-based electrocatalysts represent an ideal solution to the replacement of costly and rarer PGM-based systems, provided that comparable or even higher performance in the process can be ensured. Of course, any transition towards a new catalysts' series needs that some other fundamental issues such as catalyst stability and durability can be fully addressed under varying operational conditions along with a reduction of energy wastes

^aInstitute of Chemistry and Processes for Energy, Environment and Health (ICPEES), ECPM, UMR 7515 CNRS-University of Strasbourg, 25 Rue Becquerel, 67087 Strasbourg Cedex 02, France. E-mail: giambastiani@unistra.fr; sergey.pronkin@unistra.fr; cuong.pham-huu@unistra.fr

^bSchool of Food and Biological Engineering, Xihua University, 610039, Chengdu, China. E-mail: xmliao@mail.xhu.edu.cn

^cInstitute of Chemistry of Organometallic Compounds, ICCOM-CNR, Consorzio INSTM, Via Madonna del Piano, 10 – 50019, Sesto F. no, Florence, Italy. E-mail: giuliano.giambastiani@iccom.cnr.it

† Electronic supplementary information (ESI) available. See DOI: [10.1039/d1ta09519f](https://doi.org/10.1039/d1ta09519f)

(generation of undesired by-products) while ensuring high process efficiency.

Supported single-metal atom catalysts (SACs) have recently emerged as promising alternatives to classical TM-based heterogeneous systems within a series of challenging catalytic transformations, including several of those conventionally carried out by PGM-based catalysts.^{11–13} Carbon-based SACs are made of atomically dispersed active metal centers within inert carbonaceous supports featured by variable morphologies and eventually doped with light hetero-elements (*i.e.* N, O, and S). Their stability and catalytic performance are largely controlled by the coordination environment of metal ions embedded in the neighboring hetero-doped carbonaceous network. Such an atomistic approach to the design and synthesis of heterogeneous catalysts has unveiled unique opportunities to process intensification and their selectivity improvement other than offering valuable solutions to the drastic reduction of the active metal loadings.^{14–18}

At odds with the deep interest aroused by SACs, as witnessed by the exponential growth of manuscripts and review articles published in the last few years, their fabrication strategy has often relied on trial-and-error approaches, where the complex chemical nature of these hybrids was frequently dictated by high-temperature etching/doping thermal phases if not by the thermal decomposition of costly and time-consuming precursors. Seminal examples of highly catalytically active materials in the form of atomically dispersed metal ions within complex carbonaceous networks were obtained by the carbonization of sophisticated coordination compounds such as metal–organic frameworks (MOFs),^{19–21} metal–organic polymers^{22,23} and a mixture of coordinating polymers with N-containing molecules.^{24,25} On a similar ground, severe chemically conditions (*i.e.* pyrolysis under NH₃, HCN or CH₃CN atmosphere) for the etching/doping of preformed C-networks or strong-acid leaching treatments for the etching/removal of unstable phases^{26,27} have often been used to obtain highly performing SACs or for improving their electrochemical performance.^{27–35}

In spite of these seminal achievements, milder chemical solutions employing costless reagents remain challenging issues to be addressed for the large-scale synthesis and implementation of these materials. Both this problem poses serious concerns to any practical exploitation of SAC technology. This is even more relevant if considering the limits of such hard synthetic strategies where both density and identity of the SA metal active phases are scarcely controlled and the catalysts produced rarely contain only discrete single-atom sites in a definite coordination environment.

We have recently described an effective and general strategy for the production of highly metal loaded and atomically dispersed Fe-based composites as performing electrocatalysts for the oxygen reduction reaction, starting from cheap and food-grade raw components in combination with key thermo-chemical etching/doping phases (a NH₃ atmosphere).²⁷ The employed methodology took advantage from a proprietary synthetic procedure originally applied to the preparation of N-enriched mesoporous carbon-based 1D–3D networks^{36–38} or organic–inorganic composites^{39–41} to be employed as metal-free

catalysts for a wide series of industrially relevant transformations. Accordingly, Fe-SAs were prepared with D-glucose (C₆H₁₂O₆) as the main C-source, ammonium carbonate [(NH₄)₂CO₃] as the N-source and citric acid (C₆H₈O₇) as a sacrificial carrier for Fe³⁺ and NH₄⁺ ions. The presence of a potentially tridentate chelating agent (*i.e.* citrate ions) was regarded as an “open gate” for water-soluble metal ions to be accommodated within a C–N network. To make a step-forward and prepare highly mesoporous and N-doped C-networks containing discrete FeN_x sites, we propose herein a deeply simplified, costless and general synthetic procedure that does not include any thermo-chemical etching/doping material treatment (NH₃, CH₃CN or HCN), adapted to the use of common inorganic hard templates (*i.e.* SiO₂ nanospheres) and porogens (*i.e.* ZnCl₂) for the control of the ultimate material morphology. The effect of macro- and meso-porous networks on the ORR performance of Fe–N–C SACs in electrocatalysis has already been a seminal precedent in the literature. While mesopores were claimed to be key channels for the reaction flow transit and for the electrolyte wetting of the whole catalyst surface area, macropores largely reduced pressure drop phenomena and facilitated the reagent accessibility to the active sites.⁴²

To this aim, citric acid was employed as a metal ion chelating agent, N-carrier and main sacrificial C-source for the production of the final composite. To provide with a higher extent of mesoporosity, we easily combined our methodology with the use of a hard template in the form of SiO₂ nanospheres and ZnCl₂ salts. While the former was thought to promote the generation of hierarchically porous structures,^{43,44} the latter was employed to prevent the undesired generation of iron carbide NPs while fostering the generation of micropores.⁴⁴

As a result, the optimized catalyst exhibited a homogeneous and relatively dense distribution of iron single-site moieties whose nature was unambiguously established on the basis of PXRD, HAADF-STEM and XAS analyses. The latter suggested the dominating presence of FeN₄ moieties within a distorted square-pyramidal coordination geometry containing an axial chlorine atom. The catalyst prepared from a cheap reagent mixture and without undergoing any costly and risky thermo-chemical treatment (*i.e.* annealing under a reactive atmosphere, NH₃, CH₃CN or HCN) showed easy and complete reproducibility other than outstanding activity, stability and alcohol tolerance when employed in ORRs in an alkaline environment. It certainly ranks among the most performing state-of-the-art ORR Fe-SAC catalysts, and the role of the hard silica template along with that of ZnCl₂ salt has been thoroughly discussed along the contribution.

2. Experimental section

2.1 Materials and chemicals

Citric acid [C₆H₈O₇ anhydrous, >99.5%, MW: 192.12 g mol^{−1}] and ammonium carbonate [(NH₄)₂CO₃, MW: 96.09 g mol^{−1}] were provided by Fisher Chemicals and ACROS Organics, respectively. Zinc chloride (ZnCl₂, anhydrous, >98%; MW: 136.286 g mol^{−1}) and silica (SiO₂, fumed nanospheres, \varnothing mean size: 7 nm) were purchased by Sigma-Aldrich. Iron(III) chloride



hexahydrate ($\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$; >98%, MW: 270.296 g mol⁻¹) and Nafion® (5 wt% in isopropanol/water) were obtained from Alfa Aesar and Fluka, respectively. Unless otherwise stated, all reagents and solvents were used as provided by commercial suppliers without any further purification/treatment.

2.2 Material synthesis

In a typical procedure, 2 g of citric acid (10.4 mmol) and 5 g of $(\text{NH}_4)_2\text{CO}_3$ (52 mmol) were dissolved in 25 mL ultrapure water (Veolia Ultra Analytique, 18.2 MΩ cm, TOC < 2 ppb). Afterwards, the solution was treated under vigorous stirring with 1.2 g of silica and a uniform gel suspension was formed. $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ (0.024 g, 0.087 mmol) and ZnCl_2 (0.2435 g, 1.75 mmol) [$\text{Fe} : \text{Zn} = 1 : 20$ mol mol⁻¹ and roughly 1 : 10 w/w] were then dissolved in 3 mL of distilled water and the resulting solution was added dropwise to the above-mentioned colloidal suspension. After stirring for 30 minutes, the mixture was transferred to an oven and dried at 110 °C overnight. The resulting solid was then crushed into a fine powder and calcined at 900 °C for 2 h in an Ar atmosphere.

The as-obtained solid was suspended in 120 mL of a 2 M NaOH solution and maintained under stirring at 80 °C for 8 h to remove the silica template. The solid recovered by successive water-washing/centrifugation/drying steps underwent a second calcination step at 900 °C for 2 h in an Ar atmosphere. The collected material was stored at room temperature in an ambient atmosphere and named hereafter as $\text{Fe}^{\text{Zn}}/\text{CNP}$ (1). For comparison, two additional samples were prepared following the above-described procedure except for the use of ZnCl_2 or SiO_2 in the mixture. These samples were indicated as Fe/CNP (2) (without ZnCl_2 in the mixture) and $\text{Fe}^{\text{Zn}}/\text{CN}$ (3) (without SiO_2 template), respectively.

2.3 Characterization techniques

Scanning electron microscopy (SEM) was carried out using a Zeiss 2600F with a resolution of 5 nm. Samples were deposited onto a double-face graphite tape in order to avoid charging effects during the measurements. The loading amount of Fe was determined by inductively coupled plasma-atomic emission spectroscopy (ICP-AES, Optima 2000 PerkinElmer Inductively Coupled Plasma (ICP) Dual Vision instrument). Transmission electron microscopy (TEM) was carried out using a JEOL 2100F working at 200 kV accelerating voltage, equipped with a probe corrector for spherical aberrations and a point-to-point resolution of 0.2 nm. X-ray photoelectron spectroscopy (XPS) measurements were performed using an ultrahigh vacuum spectrometer equipped with a RESOLVE 120 MCD5 hemispherical electron analyzer. The Al K α line (Al K α , $h\nu = 1486.6$ eV) of a dual anode X-ray source was used as the incident radiation. The constant pass energy mode with pass energies of 100 and 20 eV was used to record survey and high-resolution spectra respectively. X-ray diffractogram (XRD) patterns were recorded with Cu K α radiation (40 mA, 45 kV) in the 10–80° 2 θ range, using a step size and step time of 0.05° and 80 s, respectively. The Raman spectra were recorded using a LabRAM ARAMIS Horiba Raman spectrometer equipped with a Peltier cooled CCD

detector. A laser line (532 nm/100 mW (YAG) with a Laser Quantum MPC600 PSU) was used to excite the sample. X-ray absorption spectroscopy (XAS) measurements were carried out in the fluorescence mode at the BL14W1 station of the Shanghai Synchrotron Radiation Facility (SSRF, 3.5 GeV, 250 mA in maximum, Si (311) double crystals). IFEFFIT software packages were used to process the data. The extended X-ray absorption fine structure (EXAFS) contribution was separated from different coordination shells using a Hanning window ($dk = 1.0 \text{ \AA}^{-1}$).

2.4 Electrochemical measurements

Each catalytic material was prepared in the form of a Nafion-based ink to be drop-casted/evaporated on a glassy carbon support of a RD or RRD electrode. In a typical procedure, 5 mg of the catalyst (powder) was dispersed in a solution containing 750 μL ultrapure water, 250 μL isopropanol and 50 μL Nafion (5 wt% in isopropanol/water). The resulting mixture was then sonicated for 30 min to get a homogeneous black ink. Afterwards, 16 μL of the ink was drop-casted onto the glassy carbon surface of the electrode (RDE Metrohm, 5 mm in diameter or RRDE PINE AFE6R2GCPT, a glassy carbon disk with a diameter of 5 mm, a Pt ring with an inner diameter of 6.5 mm and an outer diameter of 7.5 mm), and left to dry under ambient conditions. By this way, a dried electrode (working electrode, WE) charged with 377 $\mu\text{g cm}^{-2}$ of catalyst was employed for electrochemical measurements in a three-electrode cell, using a Ag/AgCl electrode and a graphite rod as the reference electrode (RE) and the counter electrode (CE), respectively. The amount of 377 $\mu\text{g cm}^{-2}$ was fixed for all catalytic materials (1–3) under study, irrespective to their different Fe-loadings determined by ICP-AES analysis. The catalyst loading was calibrated in accordance with the highest number of exchanged electrons (n_{e}) measured in ORRs with the model catalyst 1 ($\text{Fe}^{\text{Zn}}/\text{CNP}$, *vide infra*). Two compartments separated by a porous glass membrane were used for housing the WE and CE, respectively. All potentials were then calibrated to the reversible hydrogen electrode (RHE) according to the following equation: $E_{\text{RHE}} = E_{\text{Ag/AgCl}} + 0.197 + 0.0592\text{pH}$. Electrochemical measurements were finally performed using a Bio-Logic SP-300 potentiostat and the EC-Lab 11.32 software. Linear sweep voltammetry (LSV) was conducted in a 0.1 M O_2 -saturated KOH electrolyte at a scan rate of 10 mV s⁻¹ and a rotating rate of 1600 rpm. For comparison, a standard Pt/C electrode (20 $\mu\text{g cm}^{-2}$ of Pt on Vulcan XC-72, E-TEK, Inc. USA) was used as the benchmark catalytic system in the electrochemical tests. The accelerated durability tests (ADT) were measured by cycling the catalysts between 0.6 and 1.0 V at a scan rate of 50 mV s⁻¹ in an O_2 atmosphere. The chronoamperometry response was collected by polarizing the catalyst at a rotating speed of 1600 rpm at 0.65 V (vs. RHE). Methanol poisoning experiments were performed in a 0.1 M O_2 -saturated KOH by the addition of 1% (v/v) of MeOH. With RDE, the number of electrons involved in the oxygen reduction reaction (ORR) was determined by the Koutecky–Levich equation (eqn (1)) as follows:

$$\frac{1}{J} = \frac{1}{J_{\text{L}}} + \frac{1}{J_{\text{K}}} = \frac{1}{B\omega^{1/2}} + \frac{1}{J_{\text{K}}} \quad (1)$$



$$B = 0.62nFC_O D_O^{2/3} \nu^{-1/6}$$

where J is the measured current density per electrode geometric surface area, J_K and J_L the kinetic and diffusion-limiting current densities respectively, ω the angular velocity (rad s^{-1}), n the number of electrons in ORR, F the Faraday constant ($96\,485\, \text{C mol}^{-1}$), C_O the bulk concentration of O_2 ($1.2 \times 10^{-6}\, \text{mol cm}^{-3}$), D_O the diffusion coefficient of O_2 in $0.1\, \text{M KOH}$ ($1.9 \times 10^{-5}\, \text{cm}^2\, \text{s}^{-1}$), and ν the kinetic viscosity of the electrolyte ($0.01\, \text{cm}^2\, \text{s}^{-1}$).

For rotation ring-disk electrode (RRDE) tests, the working electrode (PINE AFE6R2GCPT, a glassy carbon disk with a diameter of 5 mm, a Pt ring with an inner diameter of 6.5 mm and an outer diameter of 7.5 mm) was prepared with the same catalyst loading while the ring potential was constantly kept at $1.2\, \text{V}$ vs. RHE. The number of electron transfer and HO_2^- yield were evaluated using the following equations (eqn (2) and (3)):

$$X_{\text{HO}_2^-} = \frac{20I_r/N}{I_d + I_r/N} \quad (2)$$

$$n_{\text{e}^-} = \frac{4I_d}{I_d + I_r/N} \quad (3)$$

where I_r and I_d are the ring and disk currents, respectively, and N (0.25) the ring collection efficiency.

3. Results and discussion


3.1 Synthesis of $\text{Fe}^{2n}/\text{CNP}$ catalyst (1) and their ZnCl_2 -free (Fe/CNP , 2) or SiO_2 -free (Fe^{2n}/CN , 3) counterparts

The synthetic procedure of new SACs takes advantage from the chelating action of the citrate polyion and its ability to generate relatively stable and water-soluble complexes with a high variety of transition metals.⁴⁵ In our synthetic scheme, citric acid plays a three-fold role: it represents the unique sacrificial C-source for the preparation of N-enriched C-based networks; it is the molecular carrier for harvesting NH_3 released from the $(\text{NH}_4)_2\text{CO}_3$ decomposition under the form of ammonium citrate $[\text{HO}-\text{C}_3\text{H}_4(\text{COO})_3\text{H}_x(\text{NH}_4)_{3-x}]$ ($x = 0-3$); it allows the

complexation of transition metal ions (*i.e.* Fe^{3+} and Zn^{2+}) and their convey within the N-doped C-material (Scheme 1). SiO_2 is an already well-known hard template for the pyrolytic generation of mesoporous C-networks.⁴⁴

The reaction of citric acid and $(\text{NH}_4)_2\text{CO}_3$ was accompanied by a vigorous CO_2 effervescence during which NH_4^+ ions were trapped in the form of tri-, di- or mono-basic ammonium citrates.^{36,37} Afterwards, Zn^{2+} and Fe^{3+} salts were added under stirring as a unique water solution. The use of a zinc salt in the synthesis of Fe-SACs is equally well known to prevent the generation of iron carbide (Fe_3C) species during material pyrolysis and to act as a porogen by favoring the generation of micropores.⁴⁴

The pH value of the resulting colloidal suspension was ≈ 8.5 , hence largely over that of the isoelectric point of a SiO_2 aqueous suspension ($\text{pH} \approx 2.5$). It implied a sticky interaction between the negatively charged surfaces of silica nanospheres and the ammonium-rich citrate frameworks. The suspension was then evaporated to dryness ($110\, \text{^{\circ}C}$ overnight), to afford a yellow-green powdery sample (Scheme 1). The latter underwent a first pyrolysis treatment ($900\, \text{^{\circ}C}$, Ar atmosphere) during which a black powder of the desired pre-catalyst was formed. Its subsequent treatment with a 2 M NaOH solution at $80\, \text{^{\circ}C}$ was employed to etch and remove the silica template⁴⁶ before submitting the sample to a second pyrolysis step (see the Experimental section for details). During the thermal phases, Zn was vaporized leaving behind micropore channels while Fe atoms remained trapped in the C/N matrix as stable FeN_x moieties (*vide infra*). The as-prepared mesoporous catalyst was the result of a long optimization procedure where variable citric acid/ $(\text{NH}_4)_2\text{CO}_3$ ratios and $\text{Fe}^{3+}/\text{Zn}^{2+}$ ratios were used. A complete account of the properties of materials obtained using various reagent ratios will be discussed elsewhere; the reagent composition described herein was selected as the best compromise between chemical composition, Fe-loading and morphological properties of SACs. The catalyst was arbitrarily named $\text{Fe}^{2n}/\text{CNP}$ (1), where Zn apex indicates the combined use

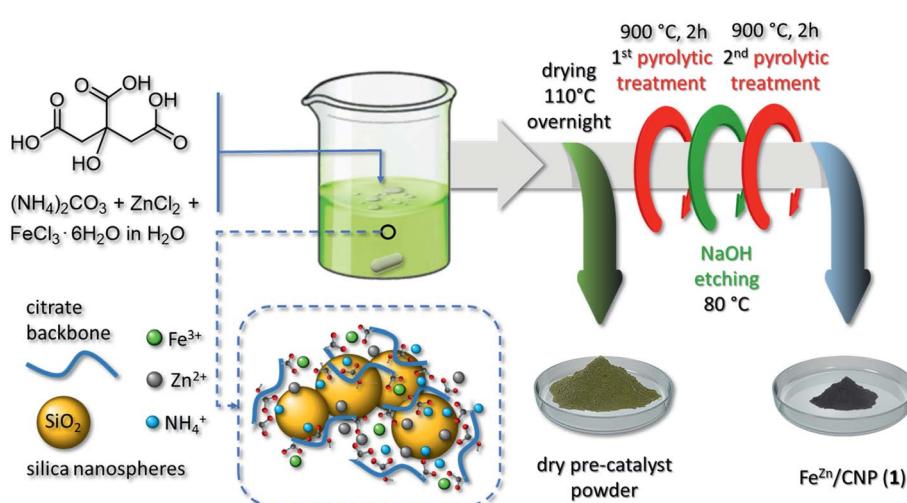

Scheme 1 Synthetic procedure for the preparation of the atomically dispersed $\text{Fe}^{2n}/\text{CNP}$ (1).



of a Zn salt while CNP stands for a C- and N-containing porous network, and it was thoroughly characterized. To address the role of the Zn salt and that of SiO_2 nanospheres in the ultimate properties of **1**, two new Fe-containing materials were prepared following the above-described synthetic procedure except for the use of ZnCl_2 (Fe/CNP, **2**) or the silica template (Fe^{Zn}/CN, **3**).

3.2 Catalyst characterization

All as-prepared materials (**1–3**) were initially analyzed with respect to their specific surface area (SSA) and pore-size distribution by N_2 physisorption analysis at the temperature of liquid nitrogen ($T = 77\text{ K}$). A comparative analysis of these data was used to assess the role of SiO_2 as the hard template and ZnCl_2 as the pore forming agent in the process. As Fig. 1A and Table 1 show, samples **1** and **2** display largely superimposable (type IV) isotherm profiles featured by moderate H3 hysteresis loop, typical of mesoporous structures with slit-shaped pores.⁴⁷ Both samples obtained from the silica nanosphere as the hard template showed a relatively high SSA (from 828 to 926 $\text{m}^2\text{ g}^{-1}$) along with a largely prevalent mesoporous nature.

It should be noticed that mesopores were certainly responsible for the slightly higher SSA value measured on sample **1**.

While the role of the SiO_2 template on the SSA and pore-size distribution of samples **1** and **2** was evident and definitively clear by comparing these material features with those of sample **3** (Table 1, entries 1, 2 vs. 3 and Fig. 1B), the role of Zn-salt as a porogen for the generation of micropores appeared under our condition less important if not negligible.⁴⁴ Indeed, the micropore component in **1** (with Zn) was even less relevant than that in **2** (without Zn; Table 1, entry 1 vs. 2). However, where the SiO_2 template did not drive the final material porosity (*i.e.* sample **3**), a carbon sample featured by small mesopores (close to the micropore region) was formed (Fig. 1B).

Wide-angle XRD profiles of the three samples at comparison (Fig. 1C) added further hints to the comprehension of the role played by SiO_2 and ZnCl_2 on the composition of **1–3**. At a first glance, the absence of the mesoporous template in **3** contributed to more extensive material graphitization. Indeed, XRD of **3** presented a relatively strong peak around 26° , corresponding to the (002) facets of graphite. At the same time, peaks located at 37.8° , 43.9° , 45.0° , 46.0° , 49.2° , and 54.5° were unambiguously indexed to Fe_3C species.⁴⁸ At odds with **3**, samples **1** and **2** presented very similar XRD patterns with two broad and distinctive peaks at ≈ 24 and $\approx 44^\circ$, typically indexed as [0 0 2]

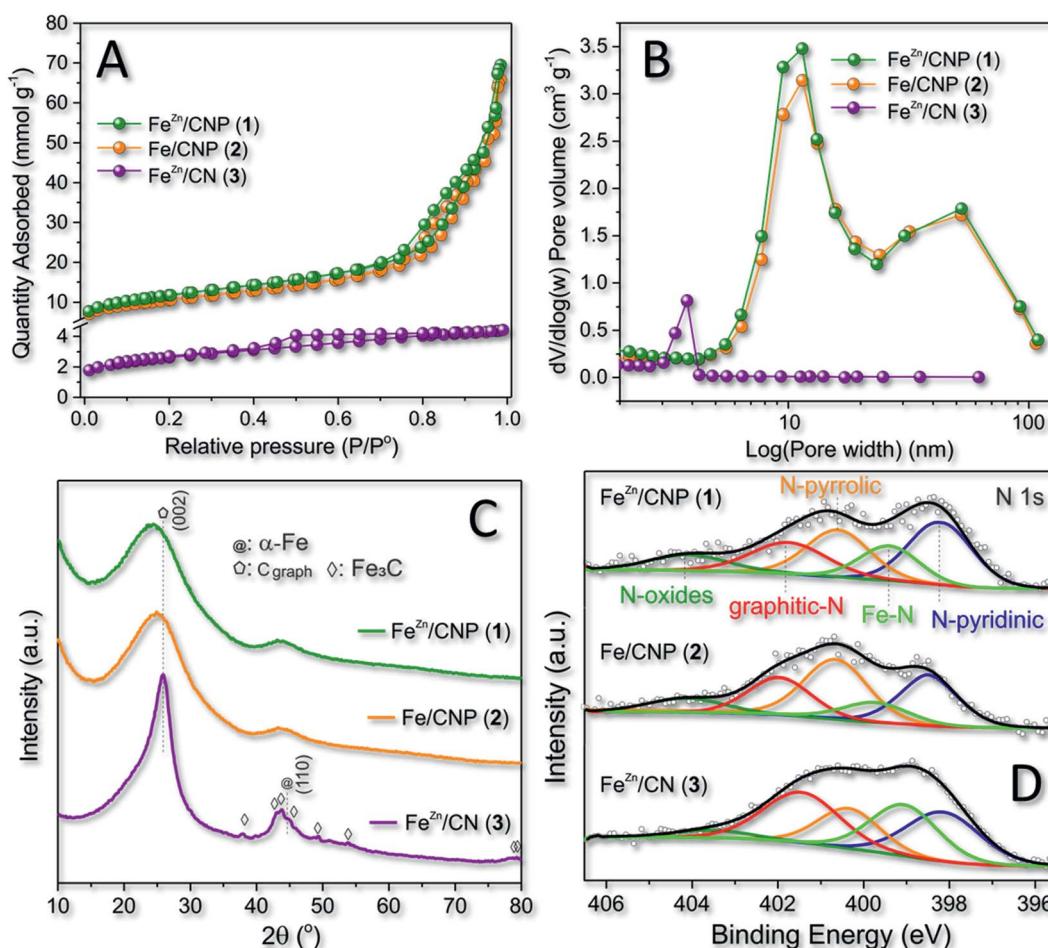


Fig. 1 (A) N_2 adsorption–desorption isotherm linear plots of Fe^{Zn}/CNP (**1**) (green curve), Fe/CNP (**2**) (orange curve) and Fe^{Zn}/CN (**3**) (violet curve) recorded at 77 K along with (B) the respective pore-size distributions (BJH method). (C) Wide-angle XRD profiles of **1–3**. (D) XPS spectra of the high-resolution N 1s core region of **1–3** with relative curve fitting.



Table 1 Textural properties and XPS analyses of samples 1–3

Entry	Sample	SSA ^a (m ² g ⁻¹)	Total pore volume ^b (cm ³ g ⁻¹)	Micropore volume ^c (cm ³ g ⁻¹)	Average pore size ^d (nm)	XPS data							
						I_D/I_G ^e	Fe ^f wt%	N ^g at%	Pyridinic	Pyrrolic	Graphitic	Oxidized	Fe-N
1	Fe ^{Zn} /CNP (1)	925	2.40	0.09	13.3	4.04	0.40	6.35	30.8	23.3	18.6	9.5	17.8
2	Fe/CNP (2)	828	2.28	0.09	14.0	4.17	0.43	6.84	28.5	29.7	21.0	9.6	11.2
3	Fe ^{Zn} /CN (3)	204	0.15	0.02	3.3	2.36	1.85	3.1	25.2	17.9	27.9	4.4	24.6

^a Brunauer–Emmett–Teller (BET) specific surface area (SSA) measured at $T = 77$ K. ^b Total pore volume determined using the adsorption branch of N_2 isotherm at $P/P_0 = 0.98$. ^c Determined by *t*-plot method. ^d Determined by BJH desorption average pore width (4V/A). ^e From Raman spectra fitted with Lorentzian peaks (Fig. S1). ^f Determined by ICP analysis on the properly digested samples. ^g Determined by XPS analysis. ^h Determined by deconvolution peaks of the high resolution XPS N 1s core region.

and [1 0 0] diffractions of mesoporous carbon samples.⁴⁹ Notably, neither **1** nor **2** seemed to be contaminated by the presence of Fe_3C as well as no peaks associated with other Fe metal phases were observed. Our experimental evidence resized the role of $ZnCl_2$ as both the porogen and the co-reagent for preventing the generation of Fe_3C species during the material thermal phases, while the use of SiO_2 seemed to hold a key role on the control of both material properties. Indeed, samples **1** and **2** prepared in the presence of SiO_2 used as the hard template possessed similar morphologies (SSA and pore-size distribution) and iron phase distributions, apparently under the form of atomically dispersed nuclei (*vide infra*). However, the Fe_3C phase was detected in **3** despite the use of $ZnCl_2$ in the mixture. Raman spectra of **1–3** (Fig. S1†) were additionally recorded for the sake of completeness to provide further details on the structural defect degree of differently synthesized mesoporous carbon networks. As Fig. S1† shows, all sample profiles were fitted by four Lorentzian peaks⁵⁰ with two dominating components at 1596 cm^{-1} and 1352 cm^{-1} , ascribed to G (graphitic) and D (disordered) bands of carbonaceous samples, respectively.⁵¹ The ratio of integrated intensity of the D and G bands (I_D/I_G) is classically claimed as a descriptive tool of the density of structural defects in C-based materials: the lower the I_D/I_G ratio, the higher the material graphitization degree. It can be inferred that samples **1** and **2** presented high disordered structures (see the I_D/I_G ratio in Table 1), whereas the material produced without SiO_2 (**3**) showed a higher graphitization extent. This latter evidence is in good accordance with the XRD results (Fig. 1C), and it was also taken as an indirect proof of the essentially atomic dispersion of iron ions in **1** and **2**. Indeed, where larger iron aggregates were formed (**3**), they could initiate metal-catalyzed graphitization paths during the high-temperature pyrolysis steps.^{52–54}

XPS survey spectra (Fig. S2† and Table 1) of **1–3** were acquired to quantitatively provide the N at% content in each sample. Deconvolution of the high-resolution profile of **1–3** at the N 1s core region was then used to establish the nature of different N-configurations available (Fig. 1D and Table 1) as well as to highlight the presence of distinctive metal–N coordination modes. Five components were assigned in the $398.2\text{--}404.2\text{ eV}$ range with those at 398.4 ± 0.2 (N-pyridinic) and $400.7 \pm 0.1\text{ eV}$ (N-pyrrolic) being the most intense for samples **1–2**. As Fig. 1D

shows, deconvolution pointed out an additional component at $399.4 \pm 0.1\text{ eV}$ that was attributed to iron-coordinated N sites (Fe–N_x) in good accordance with seminal literature precedents.^{43,54–56} As far as the iron loading in samples **1–2** was concerned, any attempt to get a semi-quantitative estimation based on XPS analysis failed due to the presumably very low metal charge. ICP-AES measurements made this possible and the measured iron content was 0.40, 0.43 and 1.85 wt% for samples **1**, **2** and **3**, respectively (Table 1).

Overall, **1** remains the sample combining the higher SSA with a supposed atomic distribution of the catalytically active sites. Moreover, the use of $ZnCl_2$ in the mixture was found to appreciably increase ($\approx 40\%$ with respect to sample **2**) the relative percentage of Fe–N active sites density in the final composite (Fig. 1D and Table 1).⁵⁷ For these reasons, **1** was selected as the catalyst for all main characterizations and catalytic trials discussed hereafter.

The morphology of **1** was examined by scanning electron microscopy (SEM, Fig. 2A and S3†) and transmission electron microscopy (TEM, Fig. 2B, D and S3†). As SEM images showed, the sample presented a homogeneous 3D hierarchical flower-like morphology made of highly intertwined and thin graphite-like sheets. TEM analysis (Fig. 2B and D) recorded at different magnifications revealed the presence of abundant pores with an average diameter between 8 and 12 nm, consistent with the average size of the nanosphere silica template. No evidence for the presence of Fe-clusters was given on the whole sample scanned area. However, high-angle annular dark-field scanning TEM (HAADF-STEM) images (Fig. 2E and F) revealed the presence of bright spots (highlighted in Fig. 2F) assigned to heavier Fe atoms in the C/N matrix. At the same time, EDX elemental mapping recorded for **1** (Fig. 2C(a–d) and S4†) showed the homogeneous distribution of C (red), N (yellow), O (light blue) and Fe (pink) elements in the sample.

The SEM images of samples **2** and **3** are also given as the ESI† material for completeness. As Fig. S5† shows, the morphology of **2** was not so different from that of **1** in accordance with the role exerted on both samples from the silica template as well as the similar SSA and pore-size distribution values (Fig. 1A and B). As far as the morphology of **3** was concerned, the absence of the SiO_2 nanosphere as the sacrificial template gave rise to substantially flat flakes of the C/N composite featured by



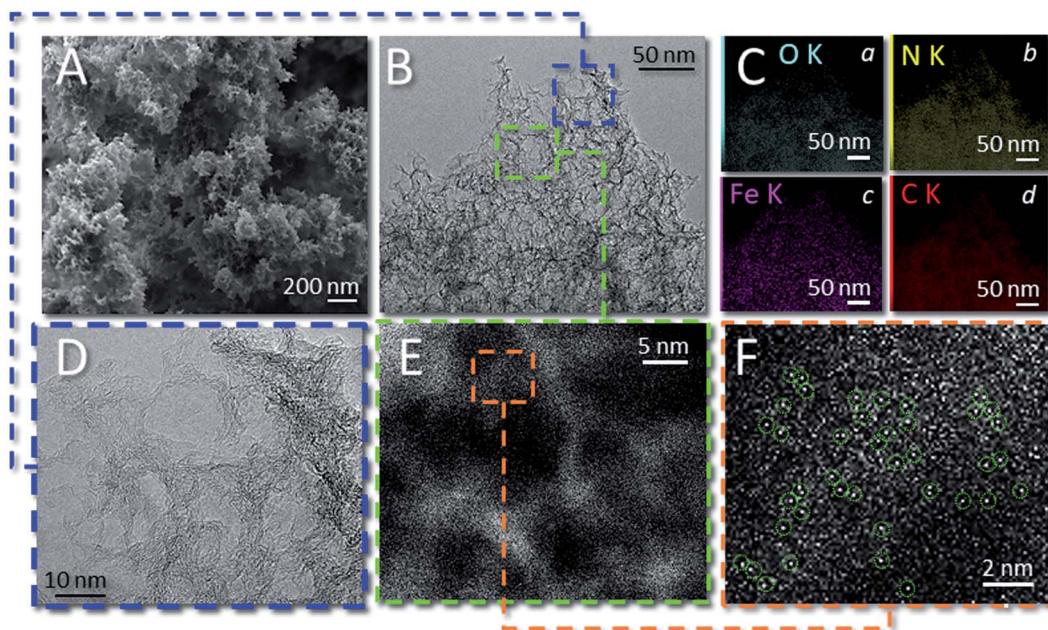


Fig. 2 (A) SEM images of **1**. (B and D) TEM images of **1** at different magnifications. (E and F) HAADF-STEM images of **1** at different magnifications. C(a-d) EDX elemental mapping for sample **1**. Color codes: C (red), N (yellow), O (light blue) and Fe (pink). (F) Highlights the bright spots assigned to heavier Fe atoms within green circles.

moderate mesoporosity, SSA and pore-size distribution (Fig. 1A and B).

The material characterization acquired for **1** was consistent with previous analyses (XPS and XRD) and thus with an atomistic distribution of the iron particles in the N-doped carbonaceous network. XPS also suggested the existence of iron species within an N-coordination sphere ($\text{Fe}-\text{N}_x$). To gain additional insights into the nature and coordination environment of iron atoms in **1**, we also performed XAS spectroscopy. Fig. 3A refers to the X-ray absorption near edge structure spectra (XANES) at the Fe K edge of **1** along with that of three common Fe^0 , Fe^{2+} and Fe^{3+} species (*i.e.* metallic Fe foil, FeO and Fe_2O_3) in comparison. It has been demonstrated that the position of pre-edge ($1s \rightarrow 3d$ transition) and edge ($1s \rightarrow 4p$ transition) resonances were sensitive to the iron oxidation state, whereas the intensity of the

pre-edge peak was related to the coordination symmetry of FeN_x species. In particular, the higher the intensity of $1s \rightarrow 3d$ transition, the lower the symmetry around the Fe sites.⁵⁸ As far as the iron oxidation state was concerned, it should be noticed that the absorption edge transition ($1s \rightarrow 4p$) of **1** was largely superimposable to that of the Fe_2O_3 reference sample, thus indicating a prevalent +3 valence for the isolated Fe atoms.⁵⁹ This was in accordance with previous reports where the pyrolysis of Fe-containing organic precursors led to the generation of iron sites in their higher valence state.^{60,61}

The phase-uncorrected Fourier transform extended X-ray absorption fine structure (FT-EXAFS, Fig. 3B) of the samples in comparison exhibited for **1** a prominent peak at 1.47 \AA , assigned to $\text{Fe}-\text{N}(\text{O})$ in the first coordination shell, while another peak centered at 2.39 \AA was ascribed for the same

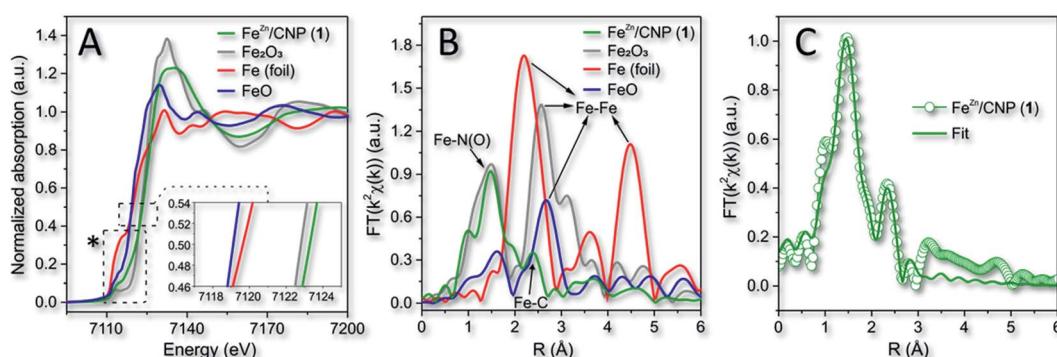


Fig. 3 (A) Normalized XANES spectra at the Fe K-edge of **1**, metallic Fe foil, FeO and Fe_2O_3 . Inset refers to the enlargement of the main edges. *See Fig. S6A† for details on pre-edge peaks. (B) k^2 -weighted Fourier transform of EXAFS data. (C) EXAFS fitting curve of **1** in R space. No phase-shift correction was applied to the Fourier transforms.



sample to the Fe–C distance of the second neighbor shell.⁶² Fe–Fe backscattering signals at 2.20 Å in the Fe foil and 2.58 Å, in FeO and Fe₂O₃ samples, respectively, were definitively absent in 1.⁶⁰ This evidence was consistent with previous conclusions based on XRD and HAADF-STEM analysis.

Fe-phthalocyanine (FePc) is traditionally benchmarked as a FeN₄ structure in a typical square-planar configuration with a high D_{4h} symmetry.⁶³ However, the latter shows a typical pre-edge peak at 7118 eV (due to a 1s → 4p_z shakedown transition),^{63,64} definitively missing in 1 (Fig. S6A†). Pre-edge peak of 1 felt at 7114 eV instead, hence revealing a slight deviation from the highly symmetric D_{4h} group.⁶⁵ The curve-fitting of FT-EXAFS (Fig. 3C and Table S1†) on 1 contributed to add further hints to the iron coordination number and its chemical environment. It unveiled an average Fe-coordinated number of ≈3.4, thus suggesting a dominating Fe–N₄ configuration in the system. Interestingly, an additional contribution to the metal coordination sphere was due to the axial coordination of a chlorine atom (Fe–Cl; Fig. 3C, S6B and Table S1†). Therefore, a distorted square-pyramidal coordination geometry of the type Cl–FeN₄ similar to that occurring in the model iron(III) *meso*-tetraphenyl porphyrin chloride (FeTPPCl) was inferred for 1. Notably, both XANES and FT-EXAFS spectra of the model molecular complex FeTPPCl^{59,64,66} showed close similarities to the profiles recorded for 1 (Fig. 3A and B). All fitting parameters listed in Table S1† suggested for 1 the presence of Fe atoms prevalently coordinated to four N atoms at 1.97 Å and to one axial chlorine atom at 2.32 Å.

The atomically dispersed nature of 1 together with the Cl–FeN₄-like structure of its active sites embedded in extensive and highly mesoporous carbonaceous networks and their well-known activity in challenging reduction processes,^{43,56,63–68} has prompted us to evaluate its performance in the model electrocatalytic oxygen reduction reaction (ORR).

3.3 Electrochemical performance of 1–3 as ORR catalysts in an alkaline environment

Cyclic voltammetry (CV) carried out in an Ar and O₂ atmosphere was initially used to assess the ability of 1 to efficiently reduce dioxygen in an alkaline environment. Finally, 2 and 3 were scrutinized under identical electrochemical conditions (0.1 M KOH as the electrolyte at a scan rate of 50 mV s^{−1}) for the sake of comparison. All CV spectra were finally plotted together in Fig. S7† for the sake of completeness. As Fig. S7† shows, all samples presented a distinct reduction peak only when CV was operated under O₂-saturated conditions. Most importantly, 1 and 2 exhibited more pronounced ORR cathode peaks with 1 revealing a positive overpotential shift with respect to 2. Such a shift suggested the ability of 1 to start the ORR process at less reduction potentials. Afterwards, RRDE voltammograms of the three samples were registered under O₂-saturated 0.1 M KOH electrolyte solution and compared with the benchmark Pt/C electrode (20 µg cm^{−2} of Pt on Vulcan XC-72, E-TEK, Inc, USA). For 1–3, the amount of the deposited catalyst was fixed to 377 µg cm^{−2} irrespective of the different Fe-loadings measured for each sample by ICP-AES analysis. The optimal loading was

assumed for the model catalyst 1 (Fe^{Zn}/CNP) in accordance with the highest number of exchanged electrons (n_E) measured in a range of catalyst weights (see also Table S2†).

Polarization curves are displayed in Fig. 4A, while the onset potential (E_{on}), half-wave potential (E_{1/2}) and kinetic current density values at 0.8 V (J_K @ 0.8 V) are detailed in Table 2. Noteworthy, 1 outperformed all catalytic materials from this series including the Pt/C reference electrode with whom it shared the E_{on} value only. E_{1/2} and J_K were undoubtedly superior in 1. The latter also showed an overpotential of about 10 mV in E_{on} with respect to its counterpart 2 prepared without ZnCl₂ and up to 60 mV with respect to 3 obtained without the use of the SiO₂ as the hard template.

At a first glance, the superior performance of 1 was attributed to the higher material specific surface area and porosity. Anyhow, its lower iron content with respect to catalysts 2 and 3 was also thought as a distinctive feature of this more performing system in ORRs. In spite of the resized role of ZnCl₂ as the porogen in the mixture of 1 under our synthetic conditions, it certainly contributed to the control of the ultimate catalyst properties and performance in electrocatalysis by preventing the generation of Fe₃C or iron clusters in general and favoring an increase of the SAFe active site density (see Table 1 and 1 vs. 2, XPS deconvoluted result). As a proof of concept, the comparative analysis of 1 and 2 pointed out the superior performance of the former in spite of its lower iron content.

The calculated kinetic current density values were as high as 41.31 mA cm^{−2} and 109.6 A g^{−1} as normalized values to the electrode geometrical area and catalyst loading, respectively. Both values were the highest measured for all investigated samples from this series. Overall, 1, besides ranking among the most performing state-of-the-art Fe-SACs ORR catalysts (Table S3†), represents an effective, cheaper, and definitively more sustainable alternative to commercial Pt-based systems for the process.

To gain additional mechanistic insights into the excellent catalytic activity of 1 in the ORR in an alkaline environment, we studied and compared the process kinetics of 1–3 and Pt/C from the respective Tafel plots (Fig. 4B). The results indicated that 1 exhibited a Tafel slope of 39.5 mV dec^{−1} whereas 2, 3 and commercial Pt/C showed slope values of 42.2, 62.9 and 57.8 mV dec^{−1}, respectively. The Tafel slope variation reflects the rate-determining step (RDS) of the process and the lower the slope value, the higher the catalyst ORR kinetic. Accordingly, 1 confirmed its superior kinetic in the ORR compared to the other electrocatalysts under study. Literature precedents led us to think that the enhanced reaction kinetics of 1 was also associated with the distinctive nature of Cl–FeN₄ single sites and the presence of an axial Cl atom.^{56,69} Li Y., Wang D. and co-workers have recently demonstrated how tuning the electronic structure of active iron centers by the near-range interaction with a coordinated chlorine atom significantly improved the catalyst ORR performance in an alkaline environment.⁴³

From a mechanism viewpoint, a Tafel slope of 39.5 mV dec^{−1} suggested that the order of reaction was −1 in OH[−], with a Fe^{III}–OH/Fe^{II}–OH₂ redox transition and a RDS associated with the generation of a superoxide Fe^{II}–O₂[−] species.⁷⁰



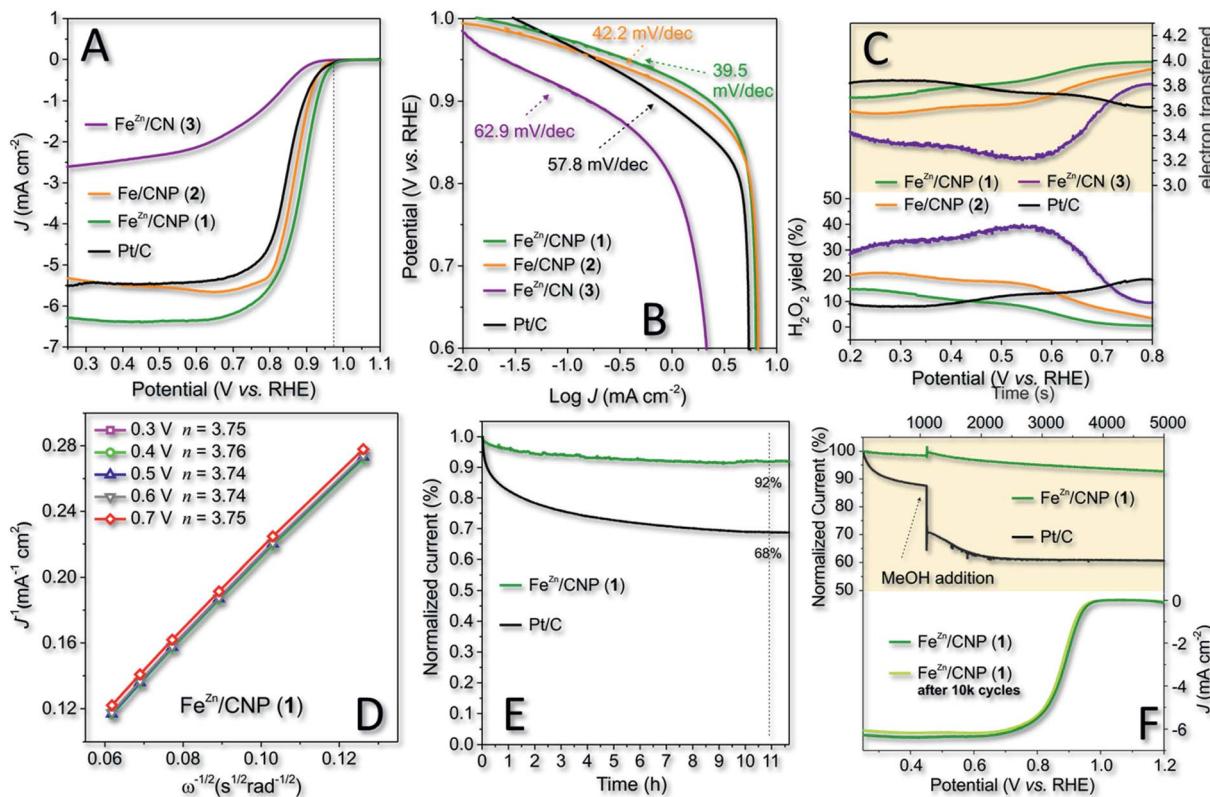


Fig. 4 (A) RRDE polarization curves of **1–3** along with that of the benchmark Pt/C ($20 \mu\text{g cm}^{-2}$ of Pt on Vulcan®), recorded in O_2 -saturated 0.1 M KOH electrolyte solution at a scan rate of 10 mV s^{-1} and a rotating electrode speed of 1600 rpm ; (B) Tafel plots of **1–3** and Pt/C ($20 \mu\text{g cm}^{-2}$ of Pt on Vulcan®); (C) electron transfer number and H_2O_2 yield plots of **1–3** and Pt/C as measured at a scan rate of 10 mV s^{-1} in an O_2 -saturated 0.1 M KOH solution ($\text{rpm} = 1600$). (D) K-L plots of **1** as obtained from the respective LSVs in the $0.3\text{--}0.7 \text{ V}$ range; (E) chronoamperometric (CA) responses of **1** and Pt/C ($20 \mu\text{g cm}^{-2}$ of Pt on Vulcan®) at comparison and at applied potential of 0.65 V ($\text{rpm} = 1600$); (F) methanol poisoning (upper side) and durability tests (bottom side) for **1**.

The ring current values measured at the Pt-ring of RRDE for **1–3** and Pt/C as electrocatalysts are summarized in Fig. 4C (bottom side), and they are expressed as the percentage of H_2O_2 produced by each catalyst as a function of the applied potential. Accordingly, the average number of electrons transferred (n_E) for each electrocatalyst in the whole range of potential values was inferred (Fig. 4C; upper side). Noteworthy, the yield of H_2O_2 ($<10\%$) produced with **1** at higher potential values ($0.45\text{--}0.8 \text{ V}$) was even lower than that measured on the benchmark Pt/C catalyst. Moreover, **1** exhibited a prevalent 4e^- reduction process within the whole range of potential values. Such a behavior at the higher potential values was consistent with

a dominant inner-sphere electron transfer (ISET) mechanism at work. However, the relatively higher production of H_2O_2 by the Pt/C catalyst at higher potentials suggested the outer-sphere electron transfer (OSET) as an operative mechanism to a larger extent on the benchmark catalyst.⁷¹ As expected, **2** and **3** offered the worse electrochemical performance with a percentage comprised between 20% and 40% of H_2O_2 produced, respectively. Accordingly, n_E was also constantly and appreciably lower than that measured for **1** in the whole scanned potential range.

Focusing on **1** as the most performing catalyst from this series, we confirmed the average number of electrons

Table 2 Electrochemical performance of all samples in the ORR

Entry	Catalyst	E_{on}^a (mV)	$E_{1/2}^b$ (V)	J_{L}^c (mA cm^{-2})	Tafel slope (mV dec^{-1})	J_{K}^d (mA cm^{-2})
1	$\text{Fe}^{\text{Zn}}/\text{CNP}$ (1)	970	0.88	6.35	39.5	41.31
3	Fe/CNP (2)	960	0.86	5.56	42.2	19.05
2	$\text{Fe}^{\text{Zn}}/\text{CN}$ (3)	910	0.77	2.45	62.9	1.8
4	Pt/C	970	0.85	5.44	57.8	25.98

^a Onset potential values *vs.* RHE. ^b Half-wave potential values reported *vs.* RHE. ^c Limited diffusion current density. ^d Kinetic current density calculated from K-L equation at 0.80 V *vs.* RHE.

transferred per O_2 molecule (n_E) as evaluated in the diffusion and kinetically limited region (0.3 to 0.7 V *vs.* RHE) by means of the Koutecky–Levich (K–L) equation.⁷² Linear sweep voltammograms (LSVs) recorded for this catalyst at variable RRDE spin rates (600–2500 rpm) are outlined in Fig. S8,† while K–L plots obtained at different potential values (from 0.3 to 0.7 V) are shown in Fig. 4D. All curves presented excellent linearity, hence implying a first-order reaction toward dissolved O_2 . Accordingly, the calculated n_E value per O_2 molecule was about 3.75, hence approaching with **1** the ideal four-electron reduction process. LSVs, K–L plots and average number of exchanged electrons (n_E) per O_2 molecule have also been acquired/calculated for catalysts **2** and **3** under identical electrochemical conditions and reported in Fig. S8† for the sake of completeness.

Finally, **1** and Pt/C electrodes were subjected to stress conditions with the aim of investigating their stability under long-term electrochemical ORR runs. In a first experiment, the chronoamperometry (CA) response of both electrocatalysts was evaluated in an O_2 -saturated atmosphere at 0.65 V for 11 h (Fig. 4E). In addition, an accelerated durability test (ADT) was performed separately on **1** by long-term cycling the catalyst in a 0.1 KOH solution, in an O_2 -saturated atmosphere at 50 mV s^{-1} as the scan rate, between 0.6 and 1.0 V (*vs.* RHE) (Fig. 4F, bottom side). As far as CA was concerned, after 11 h continuous operational tests, **1** retained about 92% of its initial current density (J). Remarkably, the CA response of commercial Pt/C after the same time was up to 26% lower than that measured on **1**, thus highlighting the superior stability of the latter. Similarly, the ADT test after 10 000 cycles showed only a negligible shift of $E_{1/2}$ in **1** towards negative values ($\approx 5\text{ mV}$), suggesting again the outstanding catalyst stability under operative conditions (Fig. 4F, bottom side).

As an additional trial, the tolerance of **1** towards alcohol poisoning was investigated. Methanol tolerance is a fundamental feature for the successful exploitation of electrocatalysts at the cathode of direct methanol fuel cells (DMFC).⁷³ Catalyst poisoning in Pt-based electrocatalysts by alcohols (crossover) is a well-known phenomenon since a long time ago.⁷⁴ Accordingly, electrochemical solutions used for the ORR with **1** and Pt/C were separately treated with a given amount of methanol (1% v/v; Fig. 4F, upper side). As Fig. 4F shows, the alcohol addition caused a sudden and irreversible decrease in the current density on Pt/C, whereas **1** maintained its electrochemical performance almost unchanged.

All these electrochemical trials taken together highlighted the remarkable catalytic activity, durability and tolerance of **1**, which therefore holds great potential for the cost-effective development of highly efficient PGM-free electrocatalysts to be applied in the ORR.

4. Conclusion

To summarize, we described a simple, cheap and highly reproducible synthetic methodology for the production of hierarchically porous N-enriched C-networks containing atomically dispersed iron sites, prevalently (if not exclusively) in the form of $\text{Cl}-\text{FeN}_4$ nuclei with the metal ion housed within

a distorted square-pyramidal coordination sphere. The synthetic protocol takes advantage of the chelating action of the citrate polyion towards a variety of transition metals for their atomic convey within the final composite. At the same time, this simple organic building block holds the key role of sacrificial C-source and NH_4^+ ion carrier in the generation of N-rich C-networks. A further sacrificial template (fused SiO_2 nanospheres) and a classical porogen (ZnCl_2) have been finally used to control the morphology and SAFe active-sites density of the composite, respectively.

The presence of a relatively high N-loading in the as-prepared material, obtained through the simple use of an inorganic leavening agent [*i.e.* $(\text{NH}_4)_2\text{CO}_3$] without incurring into more risky and costly thermo-chemical treatments for the sample doping/etching, adds further relevance to the described protocol.

Nonetheless, the outstanding electrochemical performance of $\text{Fe}^{2+}/\text{CNP}$ (**1**), its stability and durability as a catalyst for the oxygen-reduction reaction (ORR) in an alkaline environment have pointed out the great potential of a simple and cost-effective procedure for the development of highly efficient PGM-free electrocatalysts.

Looking beyond the nature and composition of the catalyst synthesized and employed in the present work, the proposed methodology remains of general application for a relatively wide series of transition metal ions that can undergo complexation/coordination by the citrate (carrier) polyion.

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

X. Z. would like to thank the China Scholarship Council (CSC) for the PhD grant during his stay at ICPEES. G. G. and C. P.-H. thank the TRAINER project (Catalysts for Transition to Renewable Energy Future) of the “Make our Planet Great Again” program (Ref. ANR-17-MPGA-0017) for support. The Italian teams would also like to thank the Italian MIUR through the PRIN 2017 Project Multi-e (20179337R7) “Multielectron transfer for the conversion of small molecules: an enabling technology for the chemical use of renewable energy” for financial support to this work. X. L. thank the National Natural Science Foundation of China (No. 21706216) and the Sichuan Science and Technology Program (2020YFG0162) for support. S. P. finally thank the Institut Carnot MICA (COM-Gra 2020) for support.

References

- 1 M. K. Debe, *Nature*, 2012, **486**, 43–51.
- 2 Q. Li, R. Cao, J. Cho and G. Wu, *Adv. Energy Mater.*, 2014, **4**, 1301415.
- 3 S. Sui, X. Wang, X. Zhou, Y. Su, S. Riffat and C.-j. Liu, *J. Mater. Chem. A*, 2017, **5**, 1808–1825.
- 4 J. Zhang, Y. Yuan, L. Gao, G. Zeng, M. Li and H. Huang, *Adv. Mater.*, 2021, **33**, 2006494.



5 M. D. Bhatt and J. Y. Lee, *Energy Fuels*, 2020, **34**, 6634–6695.

6 X. Huang, T. Shen, S. Sun and Y. Hou, *ACS Appl. Mater. Interfaces*, 2021, **13**, 6989–7003.

7 X. Wang, Z. Li, Y. Qu, T. Yuan, W. Wang, Y. Wu and Y. Li, *Chem*, 2019, **5**, 1486–1511.

8 M. Shao, Q. Chang, J.-P. Dodelet and R. Chenitz, *Chem. Rev.*, 2016, **116**, 3594–3657.

9 C. W. Bezerra, L. Zhang, K. Lee, H. Liu, A. L. Marques, E. P. Marques, H. Wang and J. Zhang, *Electrochim. Acta*, 2008, **53**, 4937–4951.

10 F. Jaouen, E. Proietti, M. Lefèvre, R. Chenitz, J.-P. Dodelet, G. Wu, H. T. Chung, C. M. Johnston and P. Zelenay, *Energy Environ. Sci.*, 2011, **4**, 114–130.

11 G. Wu, K. L. More, C. M. Johnston and P. Zelenay, *Science*, 2011, **332**, 443–447.

12 M. Lefèvre, E. Proietti, F. Jaouen and J.-P. Dodelet, *Science*, 2009, **324**, 71–74.

13 H. T. Chung, D. A. Cullen, D. Higgins, B. T. Snead, E. F. Holby, K. L. More and P. Zelenay, *Science*, 2017, **357**, 479–484.

14 B. Singh, M. B. Gawande, A. D. Kute, R. S. Varma, P. Fornasiero, P. McNeice, R. V. Jagadeesh, M. Beller and R. Zboril, *Chem. Rev.*, 2021, **121**, 13620–13697.

15 X.-F. Yang, A. Wang, B. Qiao, J. Li, J. Liu and T. Zhang, *Acc. Chem. Res.*, 2013, **46**, 1740–1748.

16 S. K. Kaiser, Z. Chen, D. F. Akl, S. Mitchell and J. Pérez-Ramírez, *Chem. Rev.*, 2020, **120**, 11703–11809.

17 J. Li, M. F. Stephanopoulos and Y. Xia, *Chem. Rev.*, 2020, **120**, 11699–11702.

18 A. Wang, J. Li and T. Zhang, *Nat. Rev. Chem.*, 2018, **2**, 65–81.

19 Y. Chen, S. Ji, Y. Wang, J. Dong, W. Chen, Z. Li, R. Shen, L. Zheng, Z. Zhuang and D. Wang, *Angew. Chem., Int. Ed.*, 2017, **56**, 6937–6941.

20 Q.-L. Zhu, W. Xia, L.-R. Zheng, R. Zou, Z. Liu and Q. Xu, *ACS Energy Lett.*, 2017, **2**, 504–511.

21 X. Chen, D.-D. Ma, B. Chen, K. Zhang, R. Zou, X.-T. Wu and Q.-L. Zhu, *Appl. Catal., B*, 2020, **267**, 118720.

22 Z. Miao, X. Wang, M. C. Tsai, Q. Jin, J. Liang, F. Ma, T. Wang, S. Zheng, B. J. Hwang and Y. Huang, *Adv. Energy Mater.*, 2018, **8**, 1801226.

23 F. L. Meng, Z. L. Wang, H. X. Zhong, J. Wang, J. M. Yan and X. B. Zhang, *Adv. Mater.*, 2016, **28**, 7948–7955.

24 L. T. Song, Z. Y. Wu, F. Zhou, H. W. Liang, Z. Y. Yu and S. H. Yu, *Small*, 2016, **12**, 6398–6406.

25 S. Zhang, H. Zhang, Q. Liu and S. Chen, *J. Mater. Chem. A*, 2013, **1**, 3302–3308.

26 X. Cui, L. Gao, S. Lei, S. Liang, J. Zhang, C. D. Sewell, W. Xue, Q. Liu, Z. Lin and Y. Yang, *Adv. Funct. Mater.*, 2021, **31**, 2009197.

27 X. Zhang, L. Truong-Phuoc, X. Liao, G. Tuci, E. Fonda, V. Papaefthymiou, S. Zafeiratos, G. Giambastiani, S. Pronkin and C. Pham-Huu, *ACS Catal.*, 2021, **11**, 8915–8928.

28 G. Lalande, D. Guay, J. Dodelet and G. Denes, *J. Electrochem. Soc.*, 1998, **145**, 2411.

29 H. Wang, R. Cote, G. Faubert, D. Guay and J. Dodelet, *J. Phys. Chem. B*, 1999, **103**, 2042–2049.

30 L. Bai, Z. Duan, X. Wen and J. Guan, *J. Catal.*, 2019, **378**, 353–362.

31 X. Cui, S. Yang, X. Yan, J. Leng, S. Shuang, P. M. Ajayan and Z. Zhang, *Adv. Funct. Mater.*, 2016, **26**, 5708–5717.

32 J. Xiao, Y. Xu, Y. Xia, J. Xi and S. Wang, *Nano Energy*, 2016, **24**, 121–129.

33 U. I. Kramm, I. Herrmann-Geppert, P. Bogdanoff and S. Fiechter, *J. Phys. Chem. C*, 2011, **115**, 23417–23427.

34 H. Perez, V. Jorda, J. Vigneron, M. Frégnaux, A. Etcheberry, A. Quinsac, Y. Leconte and O. Sublemonier, *C*, 2019, **5**, 26.

35 B. Stöhr, H. P. Boehm and R. Schlögl, *Carbon*, 1991, **29**, 707–720.

36 H. Ba, Y. Liu, L. Truong-Phuoc, C. Duong-Viet, X. Mu, W. H. Doh, T. Tran-Thanh, W. Baaziz, L. Nguyen-Dinh and J.-M. Nhut, *Chem. Commun.*, 2015, **51**, 14393–14396.

37 H. Ba, Y. Liu, L. Truong-Phuoc, C. Duong-Viet, J.-M. Nhut, D. L. Nguyen, O. Ersen, G. Tuci, G. Giambastiani and C. Pham-Huu, *ACS Catal.*, 2016, **6**, 1408–1419.

38 C. Pham-Huu, G. Giambastiani, Y. Liu, H. Ba, L. Nguyen-Dinh and J.-M. Nhut, Method for preparing highly nitrogen-doped mesoporous carbon composites, EP 3047905 A1, 2016.

39 H. Ba, J. Luo, Y. Liu, C. Duong-Viet, G. Tuci, G. Giambastiani, J.-M. Nhut, L. Nguyen-Dinh, O. Ersen, D. S. Su and C. Pham-Huu, *Appl. Catal., B*, 2017, **200**, 343–350.

40 C. Duong-Viet, J.-M. Nhut, T. Truong-Huu, G. Tuci, L. Nguyen-Dinh, Y. Liu, C. Pham, G. Giambastiani and C. Pham-Huu, *Catal. Sci. Technol.*, 2020, **10**, 5487–5500.

41 C. Duong-Viet, J.-M. Nhut, T. Truong-Huu, G. Tuci, L. Nguyen-Dinh, C. Pham, G. Giambastiani and C. Pham-Huu, *Catalysts*, 2021, **11**, 226.

42 S. H. Lee, J. Kim, D. Y. Chung, J. M. Yoo, H. S. Lee, M. J. Kim, B. S. Mun, S. G. Kwon, Y.-E. Sung and T. Hyeon, *J. Am. Chem. Soc.*, 2019, **141**, 2035–2045.

43 Y. Han, Y. Wang, R. Xu, W. Chen, L. Zheng, A. Han, Y. Zhu, J. Zhang, H. Zhang, J. Luo, C. Chen, Q. Peng, D. Wang and Y. Li, *Energy Environ. Sci.*, 2018, **11**, 2348–2352.

44 G. Chen, P. Liu, Z. Liao, F. Sun, Y. He, H. Zhong, T. Zhang, E. Zschech, M. Chen and G. Wu, *Adv. Mater.*, 2020, **32**, 1907399.

45 T. A. Hudson, K. J. Berry, B. Moubaraki, K. S. Murray and R. Robson, *Inorg. Chem.*, 2006, **45**, 3549–3556.

46 R. Ma, G. Lin, Q. Ju, W. Tang, G. Chen, Z. Chen, Q. Liu, M. Yang, Y. Lu and J. Wang, *Appl. Catal., B*, 2020, **265**, 118593.

47 K. S. Sing, D. Everett, R. Haul, L. Moscou, R. Pierotti, J. Rouquerol and T. Siemieniewska, *Pure Appl. Chem.*, 1985, **57**, 603–619.

48 G. Ren, X. Lu, Y. Li, Y. Zhu, L. Dai and L. Jiang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 4118–4125.

49 Y. Wang, X. Bai, F. Wang, H. Qin, C. Yin, S. Kang, X. Li, Y. Zuo and L. Cui, *Sci. Rep.*, 2016, **6**, 26673.

50 H. J. Seong and A. L. Boehman, *Energy Fuels*, 2013, **27**, 1613–1624.

51 F. Tuinstra and J. L. Koenig, *J. Chem. Phys.*, 1970, **53**, 1126–1130.



52 Z. Zhang, J. Sun, F. Wang and L. Dai, *Angew. Chem., Int. Ed.*, 2018, **57**, 9038–9043.

53 D. Zhai, H. Du, B. Li, Y. Zhu and F. Kang, *Carbon*, 2011, **49**, 725–729.

54 X. Ao, W. Zhang, Z. Li, J.-G. Li, L. Soule, X. Huang, W.-H. Chiang, H. M. Chen, C. Wang and M. Liu, *ACS Nano*, 2019, **13**, 11853–11862.

55 Q. Li, H. Liu, L.-C. Zhang, H. Chen, H. Zhu, Y. Wu, M. Xu and S.-J. Bao, *J. Power Sources*, 2020, **449**, 227497.

56 Z. Li, R. Wu, S. Xiao, Y. Yang, L. Lai, J. S. Chen and Y. Chen, *Chem. Eng. J.*, 2022, **430**, 132882.

57 J.-C. Li, Z.-Q. Yang, D.-M. Tang, L. Zhang, P.-X. Hou, S.-Y. Zhao, C. Liu, M. Cheng, G.-X. Li and F. Zhang, *NPG Asia Mater.*, 2018, **10**, e461.

58 C. Genovese, M. E. Schuster, E. K. Gibson, D. Gianolio, V. Posligua, R. Grau-Crespo, G. Cibin, P. P. Wells, D. Garai and V. Solokha, *Nat. Commun.*, 2018, **9**, 1–12.

59 J. Gu, C.-S. Hsu, L. Bai, H. M. Chen and X. Hu, *Science*, 2019, **364**, 1091–1094.

60 T. N. Huan, N. Ranjbar, G. Rousse, M. Sougrati, A. Zitolo, V. Mougel, F. Jaouen and M. Fontecave, *ACS Catal.*, 2017, **7**, 1520–1525.

61 W. Liu, L. Zhang, X. Liu, X. Liu, X. Yang, S. Miao, W. Wang, A. Wang and T. Zhang, *J. Am. Chem. Soc.*, 2017, **139**, 10790–10798.

62 W.-J. Jiang, L. Gu, L. Li, Y. Zhang, X. Zhang, L.-J. Zhang, J.-Q. Wang, J.-S. Hu, Z. Wei and L.-J. Wan, *J. Am. Chem. Soc.*, 2016, **138**, 3570–3578.

63 A. Zitolo, V. Goellner, V. Armel, M.-T. Sougrati, T. Mineva, L. Stievano, E. Fonda and F. Jaouen, *Nat. Mater.*, 2015, **14**, 937–942.

64 Q. Jia, N. Ramaswamy, H. Hafiz, U. Tylus, K. Strickland, G. Wu, B. Barbiellini, A. Bansil, E. F. Holby, P. Zelenay and S. Mukerjee, *ACS Nano*, 2015, **9**, 12496–12505.

65 N. Ramaswamy, U. Tylus, Q. Jia and S. Mukerjee, *J. Am. Chem. Soc.*, 2013, **135**, 15443–15449.

66 H. Li, Z. Zhang, M. Dou and F. Wang, *Chem.-Eur. J.*, 2018, **24**, 8848–8856.

67 D. J. Wasylenko, C. Rodríguez, M. L. Pegis and J. M. Mayer, *J. Am. Chem. Soc.*, 2014, **136**, 12544–12547.

68 Y. Feng and N. Alonso-Vante, *Phys. Status Solidi B*, 2008, **245**, 1792–1806.

69 Z. Cao, S. B. Zunate, X. Sun, J. Liu, E. M. Hale, W. P. Carson, S. B. Tyndall, J. Xu, X. Liu, X. Liu, C. Song, J.-H. Luo, M.-J. Cheng, X. Wen and W. Liu, *Angew. Chem., Int. Ed.*, 2018, **57**, 12675–12679.

70 J. H. Zagal and M. T. Koper, *Angew. Chem., Int. Ed.*, 2016, **55**, 14510–14521.

71 N. Ramaswamy and S. Mukerjee, *Adv. Phys. Chem.*, 2012, **2012**, 491604.

72 A. J. Bard and L. R. Faulkner, *Electrochemical Methods: Fundamentals and Applications*, John Wiley & Sons, Inc., New York, 2nd edn, 2001.

73 C. Y. Du, T. S. Zhao and W. W. Yang, *Electrochim. Acta*, 2007, **52**, 5266–5271.

74 Y. M. Tan, C. F. Xu, G. X. Chen, N. F. Zheng and Q. J. Xie, *Energy Environ. Sci.*, 2012, **5**, 6923–6927.

