

Materials Advances

Volume 4
Number 13
7 July 2023
Pages 2687–2876

rsc.li/materials-advances



ISSN 2633-5409

REVIEW ARTICLE


Ahmadreza Ghaffarkhah, Mohammad Arjmand *et al.*
2D nanomaterial aerogels integrated with phase change
materials: a comprehensive review

Cite this: *Mater. Adv.*, 2023,
4, 2698Received 27th January 2023,
Accepted 1st May 2023

DOI: 10.1039/d3ma00049d

rsc.li/materials-advances

2D nanomaterial aerogels integrated with phase change materials: a comprehensive review

Sara Rostami, Ahmadreza Ghaffarkhah,* Ali Akbar Isari, Seyyed Alireza Hashemi and Mohammad Arjmand *

Aerogels of 2D nanomaterials are considered ideal platforms for encapsulating phase change materials (PCMs) due to their unique properties, including their light weight, high porosity, large specific surface area, adjustable thermal/electrical conductivity, and mechanical flexibility, which allows for rationalizing phase transformation behaviors. The combination of these versatile aerogels and PCMs is a significant milestone in pioneering advanced composite PCMs, where multifunctionality and low cost are of utmost importance. This review provides a systematic overview of the state-of-the-art advances in 2D nanomaterial-based aerogel fabrication, including drying approaches and pre-treatment methods, as well as their potential uses in composite PCMs. It also highlights the versatile roles of different aerogels in composite PCMs and the relationships between their inherent characteristics and functionalities. This review mainly aims to increase interest in interdisciplinary research and provide guidance for the rational design of advanced multifunctional 2D aerogel-based composite PCMs, thus facilitating significant breakthroughs in both fundamental research and commercial applications.

1. Introduction

The impact of environmental concerns on human life is widespread, with the consumption of fossil fuels being a major contributor to climate change, resulting in many environmental challenges.^{1–4} In recent years, energy management has been

advanced to address these issues by implementing sustainable, low-cost energy sources. One important aspect of this effort is thermal energy storage, which plays a vital role in the prevalent adoption of renewable energy sources. Phase change materials (PCMs) are a crucial component of thermal energy management, as they can absorb and release large amounts of heat during phase transitions, rendering them well-suited for a wide range of industrial and residential applications.^{5–9} Depending on the specific conditions, these so-called “smart energy management materials” can store energy through melting/solidifying and

Nanomaterials and Polymer Nanocomposites Laboratory, School of Engineering, University of British Columbia, Kelowna, BC, V1V 1V7, Canada.
E-mail: ah.ghaffarkhah@ubc.ca, mohammad.arjmand@ubc.ca



Sara Rostami

Sara Rostami is currently serving as a Visiting International Research Student (VIRS) at the School of Engineering, University of British Columbia, Okanagan Campus. She is working under the guidance of Dr Mohammad Arjmand, and her research mainly centers on thermal management systems, PCMs, and nanomaterials. Furthermore, Sara is also actively involved in exploring the domains of 3D printing and liquid-in-liquid printing of hydrogels and inks based on 2D nanomaterials.



Ahmadreza Ghaffarkhah

Ahmadreza Ghaffarkhah is a PhD candidate in the School of Engineering at the University of British Columbia, Okanagan Campus. His research interests include the synthesis of carbon-based nanomaterials and MOFs, polymer processing and forming, and intrinsically conductive polymers. Additionally, he works on 3D printing and liquid-in-liquid printing of carbon-based hydrogels and inks. Google scholar: <https://scholar.google.com/citations?user=bZSCwa4AAA&hl=en>.



release it with a minimal loss.^{10–13} PCMs can be classified into solid–gas, liquid–gas, solid–solid, and solid–liquid systems based on the type of phase transition.^{6,14,15} Amongst all, solid–liquid PCMs have shown promise due to their higher phase change enthalpies and less volume change compared to solid–solid and liquid/solid–gas systems, respectively.^{16–19}

Solid–liquid PCMs are broadly divided into two subcategories: inorganic and organic.²⁰ Inorganic PCMs, like hydrated salts, salts, and metals, possess high volumetric latent heat and storage capacity, but they may suffer from issues such as high density, chemical instability, and low availability.²¹ Organic PCMs, such as paraffin, alcohols, and fatty acids, exhibit characteristics like congruent melting, self-nucleation, and non-corrosiveness, which allow them to be used in a wide range of practical applications.^{22,23} However, they may have drawbacks such as low thermal conductivity and liquid phase leakage, hindering far-ranging applications of PCMs.^{24–26} These challenges are addressed in recent studies by incorporating thermally conductive micro-to-nano additives, such as carbons, metals, and metal

oxides, to enhance thermal conductivity and improve the performance or to encapsulate PCMs.^{11,27–32} In this regard, nano-materials of the carbon family have been researched extensively due to their exceptional thermal conductivity reaching up to $4000 \text{ W m}^{-1} \text{ K}^{-1}$.^{33,34} For instance, the combination of expanded graphite/cellulose nanofibers (CNFs)/boron nitride (BN) with polyethylene glycol (PEG) 4000 showcased a thermal conductivity of $0.32 \text{ W m}^{-1} \text{ K}^{-1}$, leading to nearly 3300% enhancement of the thermal conductivity of the pristine PEG.³⁵

Another promising approach in thermal energy storage management is the encapsulation of PCMs, which can be achieved through two main methods: microencapsulation and nanoencapsulation.^{36–39} Microencapsulation involves enclosing PCMs in a shell made of organic, inorganic, or polymeric materials. On the other hand, nanoencapsulation involves infiltrating PCMs into porous materials such as aerogels. Nanoencapsulation not only improves the thermal conductivity, melting, and solidification rate of PCMs but also enhances their form stability.^{40–43} Energy storage reinforcement of form-stable composite PCMs explicitly relies on the structure and properties of the ESI.^{44–47} As a cutting-edge concept, aerogels, known as hyper-porous nanostructures, have been proposed as supporting scaffolds to confine PCMs.^{48–52} Additionally, the properties of the aerogels used for encapsulation can be integrated into composite PCMs to create multifunctional thermal management systems. For example, by combining conductive aerogels with PCMs, it is possible to achieve both thermal insulation and sensing/electromagnetic interference (EMI) shielding simultaneously.^{53–60}

In the field of aerogel-based PCMs, the use of 2D nanomaterials like graphene, MXene, and hexagonal boron nitride (h-BN) has been demonstrated to have exceptional thermal conductivity and high capacity for loading PCMs. These 2D nanomaterial-based aerogels have properties that make them suitable to be used as multifunctional composite PCMs,



Ali Akbar Isari

Aliakbar Isari is a PhD student at the University of British Columbia, Okanagan Campus School of Engineering. He has been working on graphene-based materials for EMI shielding and oil absorption applications. His research interest includes the synthesis of carbon-based nanomaterials, aerogels, photocatalysis, and emulsion printing.



Seyyed Alireza Hashemi

Seyyed Alireza Hashemi is a PhD student of Mechanical Engineering at the University of British Columbia, Okanagan Campus. His research focuses on the design and development of 2D carbonaceous nanomaterials, hybrid aerogels based on interfacial complexation, 3D-printed conductive constructs, advanced electromagnetic shields, and piezoresistive sensors.



Mohammad Arjmand

Dr Mohammad Arjmand is a leading and award-winning researcher in the areas of nanotechnology and polymer science and engineering. Dr Arjmand is an assistant professor (since 2018) at the University of British Columbia, Okanagan campus (UBCO). He is also a Canada Research Chair in Advanced Materials and Polymer Engineering and the technical lead of the Plastic Recycling Research Cluster at UBCO. Dr Arjmand

directs Nanomaterials and Polymer Nanocomposites Laboratory (NPNL), which focuses on the synthesis and engineering of multifunctional nanomaterials and polymer nanocomposites. Prior to joining UBCO, Dr Arjmand was a postdoctoral fellow at the Universities of Calgary and Toronto.



organic, inorganic, or polymeric materials. On the other hand, nanoencapsulation involves infiltrating PCMs into porous structures such as aerogels to create form-stable structures. Both methods offer a versatile solution to managing thermal energy storage while maintaining high heat storage performance.^{40,86–88}

Depending on the dimensions of the supporting materials, confinement strategies are categorized into four subclasses, including core-shell (0D), longitudinal (1D), interface (2D), and porous (3D) confinements.⁸⁹ 0D confinement is defined as encapsulating PCMs with a protective layer through a core-shell structure, while 1D confinement is based on embedding

PCMs into the inner cavity of nanofibrous materials such as CNTs. It is also possible to lock PCMs between the layers of various 2D nanomaterials, *e.g.*, graphene, MXene, and h-BN, through the interfacial interaction of the nanoparticles' surface and PCM molecules. Finally, in 3D confinement, aerogels are used as a template or holder to host PCMs in the interconnected nanoporous framework. Among various approaches for confinement, the encapsulation of PCMs within aerogels has emerged as a highly effective method for mitigating the issue of liquid phase leakage, as evidenced by Table 1. Furthermore, the resulting aerogel-based composite PCMs acquire the versatile

Table 1 A summary of the thermophysical properties and noteworthy practices for confined PCM composites

Type of confinement	Supporting material	PCM	K_c^a (W m ⁻¹ K ⁻¹)	T_m^b (°C)	ΔH_m^c (J g ⁻¹)	Key points	Ref.
0D	Silica	Na ₂ SO ₄ ·10H ₂ O	—	—	180.7	Subcooling of salt hydrate suppressed	90
	Silica	Octadecane	—	26.5–27.9	93.2–107.5	Confinement causes significant shift in crystallization points	91
	Silica	Stearic acid	—	84.9	276–286	Formation of stable H-bonding increases latent heat by 36.9%.	92
	Al ₂ O ₃	Paraffin wax	0.253	62.6	137	CuO and Al ₂ O ₃ nanoparticles reduce supercooling of PCM by 40% and 31.42%, respectively	29
	CuO ALOOH	Paraffin wax Palmitic acid	0.289 0.16–0.84	62.2 12.7–16.0	134 19.0–27.8	Melting temperature decreases by more than 50 °C.	93
1D	Cellulose acetate	PEG	—	60.6–69.1	0.5–56.7	The confinement dimension had an influence on the crystallization of PEG.	94
	CNT	Paraffin wax	—	46.9	26.5	A relatively wide working temperature range.	95
	CNT	Paraffin wax	—	49	123.9	Near the inner wall of the CNTs, paraffin molecules displayed an organized structural arrangement.	96
2D	GO	PEG	—	69.6	—	The freezing point of PEG has been decreased by 14 °C, while the melting temperature remains unchanged.	97
	GO/Ti ₃ C ₂ T _x	Stearic acid	—	98.7–98.8	108.5–139.3	The confinement raises the activation energy required for crystallization of stearic acid, resulting in the creation of distinct layers such as non-phase transition layer, transitional confinement layer, and proximate bulk layer.	98
3D	Graphene/ polyvinylidene fluoride- hexafluoropropylene (PVDFHFP) aerogel	Paraffin wax	0.28–0.32	28	154.6	The composite material that was developed demonstrated exceptional thermal properties, long-lasting cycle stability, impressive flexibility, and remarkable solar-thermal conversion capability. Moreover, the composite PCM exhibited a phase change enthalpy of 154.64 J g ⁻¹ and maintained its stability even after undergoing 500 cycles of heating and cooling.	99
	Polyimide/graphene/Fe ₃ O ₄ hybrid aerogel films	PEG	0.12–0.22	~65	158	The hybrid aerogel films showcased a remarkable ability to achieve a high loading capacity of PEG reaching almost 90 weight percent, thanks to their unique macroporous structure and extensive pore volume. The resulting composite PCMs demonstrated exceptional stability even after being subjected to 500 consecutive heating-cooling cycles ranging between 0 and 100 °C. This multifunctional structure offers promising prospects in the fields of EMI shielding and thermal management.	100
	Cellulose nanocrystal/konjac glucomannan/Ti ₃ C ₂ T _x aerogel	Paraffin wax	—	52.9	215.7	The findings indicate that the composite PCMs obtained possess significant reusable stability, excellent EMI shielding properties, and exceptional capabilities for managing thermal energy.	101
	Polyimide/phosphorene (PR) hybrid aerogel	PEG	—	~62–65	150	The prepared composite material possesses a flexible and foldable nature, and exhibits distinctive features that are designed for infrared stealth and thermal camouflage purposes.	56

^a Thermal conductivity of composite PCM. ^b Melting temperature. ^c Melting latent heat.



properties of aerogels, thereby broadening the potential scope of their applications.⁸⁹

3. Aerogels

Aerogels are a class of synthetic porous ultra-lightweight material derived from a gel. For the fabrication of aerogels, the liquid component of the gel is replaced with gas while maintaining the dried structure without significant collapse of the spatial network.^{102,103} Benefiting from exceptionally high porosity, large specific surface area, and ultra-low density, aerogels have been funded for many applications in aerospace engineering, energy harvesting, energy storage, tissue engineering, and environmental remediation applications.^{104–107} Subsequently, having entered the realm of nanotechnology by coupling nanomaterials with a variety of matrix materials, multifunctional composite aerogels have advanced in diverse applications ranging from thermal insulation to pollutant detection.^{108,109} Amongst all, owing to superb thermal properties, mechanical flexibility, and being atomically thin, the incorporation of 2D-nanomaterials like graphene, MXene, transition metal dichalcogenides (TMDCs)/transition metal oxides (TMOs), carbon nitride (CN), and BN into aerogels has strikingly attracted interest in recent years.^{107,110–115} For example, carbon containing nanomaterials such as graphene and MXene have been incorporated into aerogels to augment the electrical conductivity and performance for applications such as supercapacitors, sensors, batteries, field-effect transistors, photodetectors, photovoltaic modules, energy storage devices, catalysis, and EMI shielding, to mention a few.^{116–124}

In recent years, aerogels of 2D nanomaterials have emerged as a significant milestone in developing high-performance composite PCMs due to their remarkable physical, textural, thermal, and mechanical properties. Ultra-low density is one of the exceptional features of these aerogels that make them ideal for the fabrication of composite PCMs.¹²⁵ To this end, lightweight composite PCMs are highly desirable for energy storage applications, as the energy storage density of composite PCMs, expressed as phase change enthalpy, typically decreases with an increase in the content of supporting materials.⁸⁹

It is worth noting that 2D nanomaterials aerogels with hierarchically porous structures, high porosity, and large specific surface area can accommodate a large quantity of PCMs, resulting in ultra-high PCM loading and increased energy storage capacity.^{126,127} In this regard, mesopores are best suited for PCM adsorption and shape stabilization due to their considerable surface tension and capillary forces. On the other hand, micropores restrict the molecular chain movement of PCMs, while macropores lack sufficient capillary forces to retain liquid PCMs. Furthermore, modifying the functional groups on the surface of 2D nanomaterials aerogel hierarchical structures can enhance the compatibility between aerogel surface chemistry and PCMs, resulting in significantly improved shape stability and increased PCM loading.^{128,129}

Another important factor in fabricating 2D nanomaterials aerogel-based composite PCMs is their unique mechanical properties. 2D nanomaterials aerogels with and sometimes

without reinforcement with various polymers are known for their stable porous interconnected networks that showcase remarkable mechanical performance under external compressive forces. The 3D confinement provided by these flexible skeletons can further expand the functionality of PCMs in advanced thermal management applications, such as thermoregulating textiles, wearable devices, and shape memory materials.⁵⁵

The following sections highlight recent trends regarding 2D nanomaterial-based functional aerogels and their fabrication processes. The guidelines provided in this section will be used in Section 4 to evaluate the most recent fabrication strategies of aerogel-based composite PCMs.

3.1. An overview of aerogel fabrication

3.1.1. Drying approaches

3.1.1.1. Freeze-drying. Drying is one of the most common methods used in the fabrication of free-standing constructs. However, during the normal drying process, capillary forces that arise from the vaporization of solvent molecules can lead to the collapse of pore structures and impact the textural properties of aerogels. To avoid this phenomenon, the freeze-drying method can be used to minimize the stresses on the pores.^{130,131} In this method, the solvent, which is typically water for 2D materials, is frozen and then sublimated under the solvent triple point condition, resulting in the evaporation of frozen solvent molecules without any substantial stress or damage to pore structures.¹³²

The instrument and aqueous precursor features before drying are the main factors that influence the properties of aerogels prepared by freeze-drying. Instrument considerations include chamber pressure, drying and freezing temperature, freezing rate, and mold type. For instance, it is important to set the freezing temperature between the glass transition temperature and the melting temperature of ice since this parameter affects the density of the aerogels. The freezing rate can also be considered a critical effecting instrument parameter during freeze-drying. Based on the report provided by Yan *et al.*,¹³³ the carbon nanotubes (CNTs)/chitosan composites prepared at lower freezing rates exhibited better mechanical properties than those at higher freezing rates. This result is ascribed to the formation of thicker lamellas and fewer dendrites at lower freezing rates.

On the other side, the physiochemical properties of precursors also have a significant role in the characteristics of aerogels. For this aim, three main pre-treatment methods, *e.g.*, chemical-induced gelation, freeze-casting, and interfacial assembly, that affect the properties of the precursor before freeze-drying are explained in the following sections.

3.1.1.1.1. Chemical-induced gelation. The development of aerogels' homogeneous networks depends on the uniform distribution of additives and nanoparticles throughout the system. Usually, the chemical-induced gelation process generates stable media with uniform distribution of nanoparticles before the drying process. Gelation occurs when colloidal particles in a sol or solution are joined to create a spatial



framework under specific temperature and pressure conditions, and the spaces of the structure are filled with a proper liquid as a dispersing phase. During the gelation process, when the concentration of nanoparticle suspensions exceeds the critical gel concentration, the attractive and repulsive forces between the sheets become unbalanced.^{134,135} As a result, the dispersion phase will become viscous and transform into an elastic colloid capable of withstanding more pressure, which is beneficial for the structure's stability.¹³⁶

An overview of chemical-induced gelation of 2D nanomaterials-based structures is shown in Table 2. Reduction of graphene oxide

(GO) using chemical agents is one of the strategies for the self-assembly or gelation of GO nanosheets.¹³⁷ To date, many reduction agents, including vitamin C,¹³⁸ hydrazine,¹³⁹ sodium borohydride,¹⁴⁰ ascorbic acid,¹⁴¹ potassium hydroxide,¹⁴² and pyrogallol,¹⁴³ have been widely used for the reduction and gelation of GO suspensions. Furthermore, combining chemical reduction and hydrothermal processes can accelerate the removal of oxygen-containing functional groups and the chemical-induced assembly of reduced graphene oxide (rGO) nanosheets. In 2019, Shen *et al.*¹⁴⁴ developed graphene aerogels using a hydrothermal-assisted method. For this aim, a proper

Table 2 Beyond chemical induced gelation for fabrication of 2D based nanomaterial aerogels

Material	Gelation agent	Preparation technique	Other	Ref.
rGO	EDA	Chemical-induced gelation	EDA was used as a reducing agent and crosslinker.	175
rGO	EDA	Freeze-drying Chemical-induced gelation and cross-linking Solvent exchange Freeze-drying	EDA was used as a reducing agent and crosslinker. The prepared GO aerogel beads were thermally reduced.	176
Ti ₃ C ₂ T _x	EDA	Chemical-induced gelation Freeze-drying	EDA was used as a crosslinker to assemble MXene nanosheets.	177
rGO/Pd	Ethylene diamine tetra acetic acid (EDTA)	Chemical-induced gelation Freeze-drying	GO aerogels were first reduced by hydrazine vapor and then thermally annealed under hydrogen gas.	178
N-doped rGO	EDA Diethylenetriamine (DETA) Tetraethylenepentamine (TEPA)	Chemical-induced gelation Freeze-drying	The bonding state of nitrogen atoms is related to the type of reducing agents.	179
Ti ₃ C ₂ T _x /GO	GO	Chemical-induced gelation Electrostatic spinning Freeze-drying	GO was used as a crosslinker for Ti ₃ C ₂ T _x .	180
Ti ₃ C ₂ T _x /rGO	GO	Chemical-induced gelation Freeze-drying Chemical reduction	GO was used as a crosslinker for Ti ₃ C ₂ T _x . The fabricated aerogels were chemically reduced <i>via</i> a mixture of hydroiodic and acetic acids.	181
GO/PVA	PVA	Chemical-induced gelation and cross-linking Freeze-drying	PVA was used as a cross-linking agent.	182
rGO	Octadecylamine (ODA)	The GO solution was dripped into a coagulation bath to achieve ODA and ethanol to achieve rGO hydrogel beads. Freeze-drying	ODA was used as a reducing agent and crosslinker. The prepared GO aerogel beads were thermally reduced.	183
Ti ₃ C ₂ T _x /calcium alginate	Ca ²⁺	Chemical-induced gelation Vacuum-assisted-filtration Freeze-drying	Divalent Ca ²⁺ ions were used as a crosslinker for Ti ₃ C ₂ T _x .	184
Ti ₃ C ₂ T _x /GO/sodium alginate	GO/Ca ²⁺	Chemical-induced gelation Freeze casting Freeze-drying	Divalent Ca ²⁺ ions were used as the main crosslinker for Ti ₃ C ₂ T _x . GO was also effective for cross-linking Ti ₃ C ₂ T _x sheets.	185
Ti ₃ C ₂ T _x	Fe ²⁺	Chemical-induced gelation Freeze-drying	Divalent Fe ²⁺ ions were used as a cross-linker for Ti ₃ C ₂ T _x .	186
Mg ²⁺ -Ti ₃ C ₂ T _x	Mg ²⁺	Chemical-induced gelation Freeze-drying	—	187
Fe ³⁺ -Ti ₃ C ₂ T _x	Metal ions	Chemical-induced gelation Freeze-drying	Different metal ions, <i>e.g.</i> , Fe ²⁺ , Al ³⁺ , Co ²⁺ , Ni ²⁺ , Mg ²⁺ , Ca ²⁺ , Mn ²⁺ , Zn ²⁺ , were used as chemical crosslinkers for MXene assembly.	156
rGO/MoO ₂	L-Ascorbic acid	Chemical-induced gelation Freeze-drying	L-Ascorbic acid was used as a reducing agent and crosslinker.	143
rGO/Au	L-Ascorbic acid/Na ₂ B ₄ O ₇	Chemical-induced gelation Freeze-drying	Na ₂ B ₄ O ₇ was used as an enhancer for reducing GO.	144
rGO	Vitamin C	Chemical-induced gelation Freeze-drying	Vitamin C was used as a reduction agent. After freeze-drying, the samples were thermally annealed.	142
rGO	NaHSO ₃	Chemical-induced gelation Freeze-drying	NaHSO ₃ was used as a reducing agent and crosslinker. The prepared GO aerogel beads were thermally reduced.	188
Ti ₃ C ₂ T _x /polyimide	—	Chemical-induced gelation BDFC Freeze-drying	First, the polyamic acid was synthesized and mixed with Ti ₃ C ₂ T _x to fabricate aerogels. The prepared structures were then thermally annealed to complete the imidization process, <i>i.e.</i> , the formation of polyimide.	189



nature, dependence on size, and association with the constant adsorption and desorption of nanomaterials.¹⁶⁵ To overcome these instabilities, the addition of oligomeric/polymeric ligands at the oil–water interface has been recognized as an efficient way to increase nanoparticle interfacial performance. In this strategy, the nanoparticles and ligands interact at the interface and create nanoparticle surfactants, allowing the nanoparticles to jam at the interface.¹⁶⁶

Interfacial assembly and jamming of nanoparticles at the liquid–liquid interface result in non-equilibrium forms of one liquid phase in another immiscible liquid. Note that these generated structured liquids are programmable due to the ability to be un-jammed and re-shaped.^{167–169} Such a programmable fabrication platform can be used as an innovative pre-treatment for large-scale fabrication of robust aerogels with well-defined micro- to macro-scale characteristics. Kamkar *et al.*¹⁷⁰ fabricated ultra-flyweight graphene-based aerogels with a density of $\sim 0.15\text{--}1.2\text{ mg cm}^{-3}$ using structured liquids of GO as a template. For this aim, aqueous suspensions of GO were injected into a non-polar domain containing PSS-[3-(2-aminoethyl)amino]propyl-heptaisobutyl substituted POSS (POSS-NH₂) and hexane to form worm-like structured liquids. In this case, the co-assembly of GO and POSS at the liquid–liquid interface generates an interfacial skin that stabilizes the aqueous phase in a non-equilibrium shape. The fabricated structures were finally kept in a freezer for 24 h and then freeze-dried for two days to construct ultra-flyweight aerogels of GO.

3.1.1.2. Supercritical drying. Supercritical drying is another method for creating aerogels at temperatures and pressures above the critical point of solvents. As the conditions exceed the critical point, the liquid phase turns into a supercritical fluid, eliminating the difference between liquid and gas phases and greatly reducing the surface tension in the solid pores.¹⁷¹ Accordingly, the pores were well-preserved during drying due to the elimination of the surface tension and capillary forces. The supercritical drying process is proven to be very effective in fabricating highly porous structures with ultra-low shrinkage or cracking during drying by operating beyond the liquid–gas boundary state.¹⁷² For instance, Cheng *et al.*¹⁷³ developed mechanically robust rGO aerogels with a relatively large specific surface area through supercritical drying. After preparing 3D rGO-based hydrogels through hydrothermal treatment and chemical reduction, the obtained gels were dried with supercritical ethanol for almost one week at operating temperature and pressure of 250 °C and 8 MPa, respectively.

3.1.1.3. Ambient temperature drying. As explained in the previous sections, supercritical-drying and freeze-drying approaches require specific equipment to achieve vacuum pressure in a few centimeter cells. Hence, their applications are limited to the fabrication of centimeter-scale aerogels, and their operating costs are high. Accordingly, ambient temperature drying, also known as air-drying, can be employed to fabricate cost-effective and large-scale aerogels of 2D nanomaterials. However, the shrinkage of liquids during evaporation and preservation of pores after drying remains challenging; therefore, suitable pre-treatment techniques should be applied

to minimize the capillary forces within the pores. Recently, Yang *et al.*¹⁷⁴ fabricated large-scale structure-intact graphene aerogels with an approximate size of 1 m² and a density of 2.8 mg cm⁻³ through ambient temperature drying. This method introduced the microbubble template to confine the GO sheets within microbubble gaps and attain structure-intact graphene hydrogel. Then, the fabricated hydrogels were frozen for 4–6 h at –18 °C and dried at 60 °C in the air for almost 12 h. The resulting aerogels showcased exceptional elasticity and ultra-low density of $<10\text{ mg cm}^{-3}$, comparable to the best practices reported for freeze-dried or critically dried graphene samples.

3.2. 2D nanomaterials in aerogel fabrication

2D nanomaterials are single or multilayered sheet-like structures with strong in-plane bonds and weak van der Waals forces between sheets.^{190,191} Graphene, metal oxides and hydroxides, dichalcogenides, polymers, BN, phosphorene, and MXenes are prime examples of 2D nanomaterials that have been synthesized through extraction, exfoliation, chemical or physical vapor deposition, and numerous wet chemical strategies.^{191,192} Benefiting from their distinct physical and chemical properties and straightforward surface functionalization, 2D nanomaterials have been vastly utilized to fabricate network-like aerogels with hierarchically arranged frameworks.^{193,194}

3.2.1. Graphene-based aerogels. Graphene is a superstar of carbonaceous nano allotropes consisting of either one or a few layers of atoms tightly packed in a hexagonal 2D honeycomb lattice. It is highlighted as the strongest material known today, with intrinsic tensile strength and Young's modulus of 130 GPa and 1 TPa, respectively.¹⁹⁵ 2D graphene nanosheets also exhibit unique thermal conductivity ($5300\text{ W m}^{-1}\text{ K}^{-1}$), optical transmittance ($\sim 97.7\%$), exceptionally large specific surface area ($\sim 2600\text{ m}^2\text{ g}^{-1}$), inherent hydrophobicity, and high carrier mobility, opening numerous opportunities ranging from smart electronics to thermal management systems.^{196–198} However, challenges regarding the synthesis of pristine graphene, along with their tendency to re-agglomerate into graphite-like powders due to the strong $\pi\text{--}\pi$ stacking and van der Waals interactions between them, dramatically limit its application in aerogel fabrication.^{195,199,200} These problems have given rise to the use of GO-based aerogels.^{201,202}

GO is readily dispersible in many solvents, its physicochemical properties can be fine-tuned over a wide range, and it can be easily assembled into 3D gel networks upon further chemical/electrochemical treatments.²⁰² However, GO is electrically insulative and, compared to pristine graphene, suffers from high oxidation levels and lattice defects. Therefore, GO or its 3D scaffolds, *e.g.*, gels and aerogels, usually undergoes chemical, thermal, or electrochemical reductions to approach charge mobility and graphene-like characteristics.^{195,201,203} For instance, Hu *et al.*²⁰² have employed chemical-induced gelation to produce ultra-light, yet highly compressible aerogels, by a two-step process. In brief, monolithic functionalized graphene hydrogels were produced by adding EDA aqueous solution as a weak reduction agent to the GO suspension. The obtained structured hydrogels were then converted into



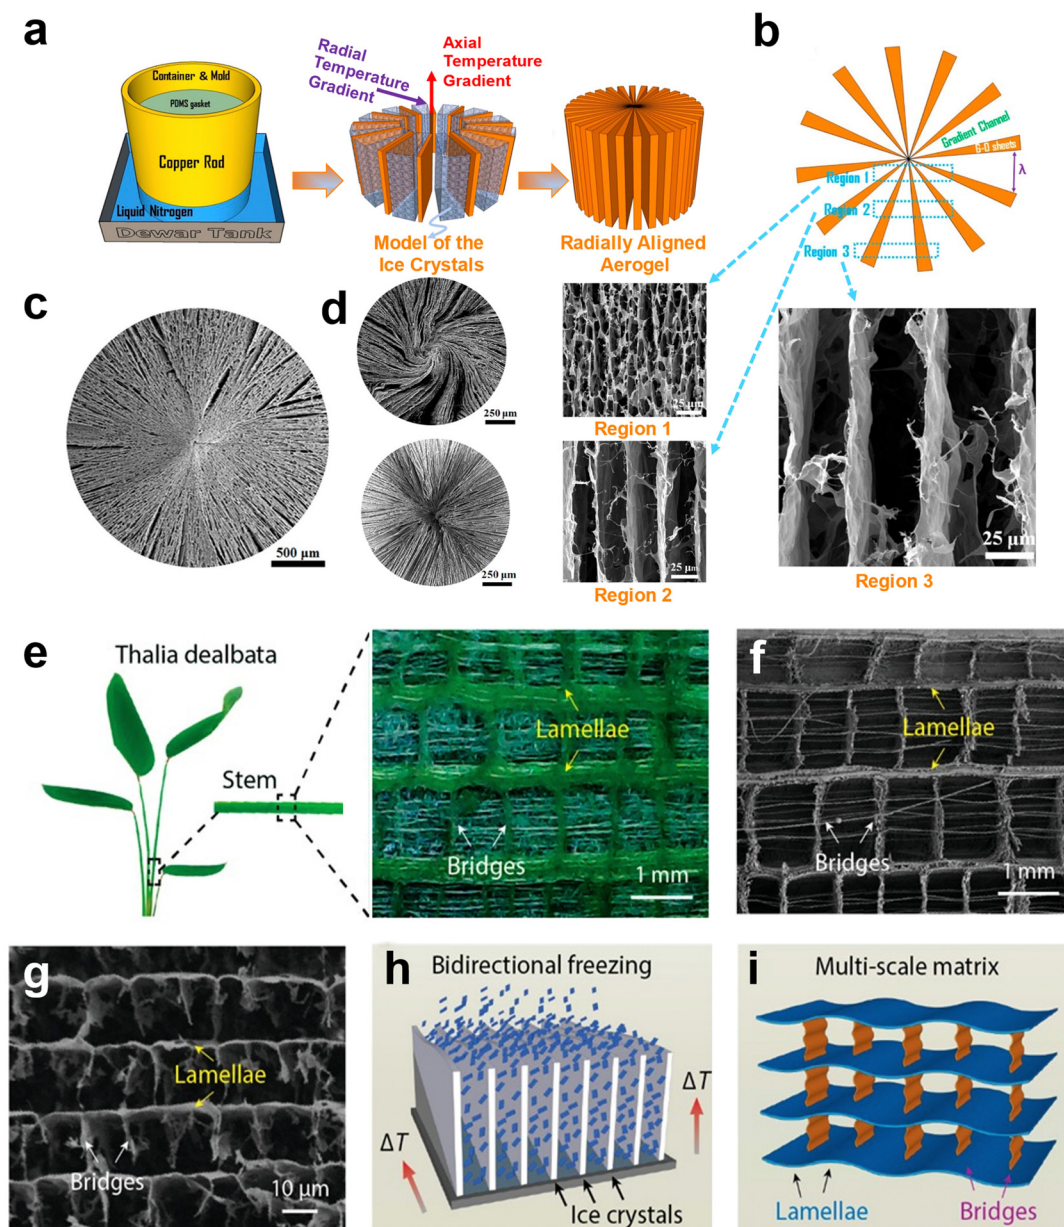


Fig. 1 (a) Schematic illustration of the BDFC method used for developing radially aligned graphene-based aerogels. (b) Cross-section SEM images of the GO-based aerogel. The widths (λ) of channels increase from center to edge, representing a radially aligned structure. (c) SEM image of radially aligned GO aerogel. (d) SEM images of GO/chitosan aerogels with either spiral or radial patterns. (a–d) Reproduced with permission.¹⁶³ Copyright 2018, American Chemical Society. (e–g) Optical image of the architecture of the *Thalia dealbata* stem and corresponding biomimetic GO-based aerogel. (e and f) An oriented lamellar layer parallel to the growth direction with interconnected bridges was observed in the optical and SEM images of the *Thalia dealbata* stem. (g) The SEM image of biomimetic graphene-based aerogels showcased oriented layers and interconnected bridges similar to those of the *Thalia dealbata* stem. (h) The formation of the ice crystals in the BDFC via a PDMS wedge. (i) The schematic of the as-prepared graphene aerogel in the format of the plant stem. (e–i) Reproduced according to the terms of ACS author choice license.²¹⁰ Copyright 2017, American Chemical Society.

Distinct electrical conductivity, hydrophilic nature, and the ability to intercalate cations and store charge led to significant interest in exploring $\text{Ti}_3\text{C}_2\text{T}_x$ for EMI shielding, strain sensing, and energy storage applications.^{227,228}

Similar to graphene, MXene-based aerogels also go through various processing steps to achieve better mechanical characteristics. To date, the freeze-casting technique, along with subsequent freeze-drying, is among the most popular

fabrication methods of $\text{Ti}_3\text{C}_2\text{T}_x$ aerogels. However, due to the weak van der Waals forces between $\text{Ti}_3\text{C}_2\text{T}_x$ sheets, polymeric binders, *e.g.*, gelatin, cellulose, PVA, *etc.*, are routinely added as a chemical glue to assemble 2D nanosheets and enhance the mechanical characteristics of the final constructs. For instance, in a recent study, gelatin molecules were introduced as a chemical binder to strengthen the interaction between $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets and fabricate 3D composite aerogels of MXene with





Fig. 2 (a) The surfactant-foaming sol-gel method uses microbubble templates to fabricate uniform rGO aerogels without freeze-drying. (b) Polarized-light optical microscope (POM) image of the foam GO solution showcasing the microbubble template. (c and d) The SEM images of graphene aerogels demonstrate the confined rGO sheets within the template's gaps. (e) Superior thermal stability of rGO aerogels. (a–e) Reproduced with permission.¹⁷⁴ Copyright 2018, American Chemical Society. (f) The GO aqueous inks were used for liquid streaming in the hexane/POSS domain. (g) Streaming GO aqueous suspensions in hexane/POSS. (h) Digital images of GO worm-like structured liquids. The prepared structures showcased dual porosities from (i) micro- to (j and k) macro-scales. (f–k) Reproduced according to the terms of the CC-BY license.¹²³ Copyright 2022, Wiley-VCH.

much enhanced yet anisotropic mechanical characteristics. In this approach, $\text{Ti}_3\text{C}_2\text{T}_x$ /gelatin homogenous suspension was cast into a rectangular aluminum-based Teflon mold and immersed in liquid nitrogen. Ice crystals grew vertically afterward, compelling $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets and gelatin molecules to be assembled in a parallel direction. Unidirectional freeze-casting followed by a freeze-drying approach endowed lightweight and highly porous $\text{Ti}_3\text{C}_2\text{T}_x$ /gelatin aerogel, indicating a -59.5 dB minimum reflection loss at 14.04 GHz with a 6.24 GHz effective absorption bandwidth.²²⁹

Scaling the unique characteristics of $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets to functional aerogels without compromising electrical conductivity and/or electrochemical activities is still challenging, particularly because traditional assembly approaches of $\text{Ti}_3\text{C}_2\text{T}_x$ aerogels mainly rely on external binders, which tremendously reduce the functionality of the final constructs. In order to address this challenge, Ding *et al.*²³⁰ developed metal ion-intercalated $\text{Ti}_3\text{C}_2\text{T}_x$ aerogels without polymeric binders showcasing distinctive electrical conductivity of 758.4 S m^{-1} , a large surface area of 140.5 m^2 g^{-1} , and high stability in aqueous



media. In brief, $\text{Ti}_3\text{C}_2\text{T}_x$ suspension was blade coated onto the polystyrene substrate and heated up to 130 °C to form a crumpled-texture $\text{Ti}_3\text{C}_2\text{T}_x$ layer. The fabricated platform was then thoroughly loaded with Mg^{2+} to induce the gelation of $\text{Ti}_3\text{C}_2\text{T}_x$. $\text{Mg}^{2+}/\text{MXene}$ hydrogels were finally freeze-dried to fabricate biomimetic aerogels featuring the hierarchical texture of *Phrynosoma cornutum*, the Texas-honored lizard (Fig. 3a–f). The $\text{Mg}^{2+}/\text{MXene}$ aerogel demonstrated outstanding EMI shielding characteristics, excellent salt adsorption properties in brackish water desalination, and exceptionally high aerial capacitance in quasi-solid-state micro-supercapacitors. In another study, unidirectional freeze-casting was used to assemble PVA and $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets into biomimetic aerogels resembling the morphology of down feathers in penguins (Fig. 3g–k). After successive oxidation and calcination of pristine $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets, spectrally modified $\text{Ti}_3\text{C}_2\text{T}_x$ were synthesized. Then PVA and $\text{Ti}_3\text{C}_2\text{T}_x$ were blended and freeze-thawed three times to obtain a hydrogel. After subsequent freeze-casting and freeze-drying, an anisotropic hierarchical structure of horizontally aligned struts with parallel porous alignments was assembled at an angle of $\sim 60^\circ$. Unlike the traditional unidirectional freeze-casting technique, this approach used PVA as an ice-structuring binder to induce dendritic growths of ice crystals from the main trunks. The high viscosity of PVA/calcinated $\text{Ti}_3\text{C}_2\text{T}_x$ suspension and the repeated freezing-thawing process hamper the growth of ice crystals along the temperature gradient and facilitate the formation of transverse ligaments at an angle to the main trunks. Such feather-like micro-porous structures were used for highly efficient solar-powered water evaporators due to their low thermal conductivity of $0.162 \text{ W m}^{-1} \text{ K}^{-1}$ and full-spectrum sunlight absorption of 98.5%.²³¹

Interfacial co-assembly and Jamming of $\text{Ti}_3\text{C}_2\text{T}_x$ and POSS-NH₂ at the toluene/water interface is another interesting procedure employed for the fabrication of functional MXene-based aerogels.²³⁵ In this emulsion system, $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets and POSS-NH₂ form an overlapping layer of MXene nanosheets, which offer a robust assembly with excellent mechanical properties upon jamming (Fig. 4a and b). The degree of $\text{Ti}_3\text{C}_2\text{T}_x$ overlap was programmed by increasing the concentration of POSS-NH₂, leading to the tunability of the final constructs. These programmable structured liquids were then used as a template to fabricate lightweight, hydrophobic, isotropic MXene aerogels with unique mechanical and electrical characteristics. Despite the hydrophilic nature of $\text{Ti}_3\text{C}_2\text{T}_x$, these aerogels showcased unique hydrophobicity that stems from the presence of POSS-NH₂ in the liquid template. This hydrophobicity, along with the highly porous structures of the fabricated aerogels, made them promising oil absorbers (Fig. 4c and d). For example, a toluene absorption of up to 9000% is found for these constructs. Furthermore, similar to other $\text{Ti}_3\text{C}_2\text{T}_x$ -based aerogels, these interfacially driven morphologies of MXene also demonstrated unique EMI shielding effectiveness of 34.5 dB at the thickness of only 2 mm.²³⁵

The metal ionic crosslinking technique is another high-paced approach that can be utilized to generate well-patterned $\text{Ti}_3\text{C}_2\text{T}_x$ hydrogels as a template for developing functional

aerogels. Through a three-step electro-gelation process, MXene hydrogels were formulated with spatial patterning and controllable resolutions down to 130 μm . First, a series of patterns that defined the final shape of hydrogels were printed on a circuit board. Then, copper, as a sacrificial metal, was electro-deposited on the Au pads of circuit boards. Finally, $\text{Ti}_3\text{C}_2\text{T}_x$ suspension was applied in the cell to accomplish the electro-gelation process, which yielded pre-defined 3D assemblies of MXene. By electrolyzing the copper, Cu^{2+} releases and initiate the electro-gelation process during which electrostatic interactions occur between cations and the $\text{Ti}_3\text{C}_2\text{T}_x$ sheets (Fig. 4e and f). This approach generates complex architecture that cannot achieve through any of the methods described before (Fig. 4g). After freeze-drying, the resultant aerogel featured a lightweight structure with a specific surface area of $68.8 \text{ m}^2 \text{ g}^{-1}$.²³⁶

3.2.3. Other 2D nanomaterials for functional aerogels.

Although graphene and MXene present remarkable physiochemical properties, other 2D materials have also been used as building blocks of aerogels. Up to now, several 2D nanomaterials, such as h-BN, molybdenum disulfide (MoS_2), and tungsten diselenide (WSe_2), have been synthesized and employed for multifunctional aerogel fabrication.²³⁷ For instance, MoS_2 has been extensively studied as a highly stable and cost-effective nanomaterial that possesses a tunable band gap.^{238–240} MoS_2 is usually hybridized with other 2D nanomaterials, including GO, to prepare functional aerogels since MoS_2 nanoflakes alone are unable to form structured scaffolds with a highly effective surface area. These MoS_2/GO aerogels demonstrated unique capability for gas sensing, thermal insulation, and energy storage.^{241–243} The potential of MoS_2/GO hybrids was highlighted by Tang *et al.*,²⁴⁴ where hybrid supercapacitors with complex geometries were fabricated by 3D printing of MoS_2/GO inks. The viscoelastic characteristics and general printability of these hybrid inks mainly relied on GO, while the addition of MoS_2 was introduced as a way to improve the printing resolution and areal capacitance of fabricated structures. Aside from MoS_2/GO inks, 2D GO nanosheets were also employed as a domain for printing other nanomaterials, including 0D silver nanodots and 1D multi-walled carbon nanotubes (MWCNTs). The process of ink fabrication and 3D printing for these hybrid aerogels is shown in Fig. 5a–c. In a typical procedure, negatively charged nanoparticles, *e.g.*, silver, MoS_2 , and MWCNTs, were added to the solution of urea, gluconic- δ -lactone, and GO. Upon increasing the temperature, mild hydrolysis of urea happened during solvent evaporation, resulting in the gelation of the hybrid inks. It is worth noting that the secondary nanoparticles were closely bound with micropores of the cross-linked GO sheets upon gelation (Fig. 5d). The prepared inks were then used for 3D printing complex and nonplanar geometries that transformed into functional aerogels upon freeze-drying, chemical reduction, and additional thermal annealing.

Aerogels of 2D h-BN are known for their unique mechanical and thermal characteristics and therefore provide potential avenues for numerous applications, including thermal management systems, gas absorption, infrared insulations, field-effect transistors, photodetectors, photovoltaic modules, energy storage devices,





Fig. 3 (a) Schematic illustration of the scalable fabrication of crumpled-texture $\text{Mg}^{2+}/\text{MXene}$ platform via Mg^{2+} -induced gelation method. The fabricated structure resembles the texture of *Phrynosoma cornutum*'s skin. (b) Digital photo of *Phrynosoma cornutum*. (c and d) Optical and SEM images of micro-ornamentations of lizard's skin that can transport water. Reproduced according to the terms of the CC-BY license.²³² Copyright 2011, Beilstein-Institute. (e) Movement of water in microchannels of *Phrynosoma cornutum*'s skin. (b and e) Reproduced according to the terms of the CC-BY license.²³³ Copyright 2015, The Royal Society. (f) Optical and SEM images of crumpled-texture MXene coating after thermal shrinkage. (a and f) Reproduced with permission.²³⁰ Copyright 2021, Wiley-VCH. (g) Schematic illustration of the multifunctional fabrication of feather-like $\text{Ti}_3\text{C}_2\text{T}_x/\text{PVA}$ aerogels. (h) Digital image of a penguin down-feather depicting structural details in multiscale. Reproduced with permission.²³⁴ Copyright 1999, Academic Press. (i–k) Digital and SEM images of the feather-like biomimetic aerogels of $\text{Ti}_3\text{C}_2\text{T}_x/\text{PVA}$. (g and i–k) Reproduced with permission.²³¹ Copyright 2022, Wiley-VCH.





Fig. 4 (a) Schematic illustration of interfacial co-assembly and jamming of $\text{Ti}_3\text{C}_2\text{T}_x$ and POSS-NH₂ at the toluene/water interface. The prepared structured liquids were used as a template for aerogel fabrication. (b–d) The prepared aerogels showcased exceptionally low density, hydrophilic nature with a water contact angle of 123°, and unique oil absorption characteristics. The yellow oil phase in (d) is *n*-hexene dissolving azobenzene. (a–d) Reproduced with permission.²³⁵ Copyright 2019, Wiley-VCH. (e) Schematic of the metal ionic cross-linking technique for producing well-patterned MXene hydrogels/aerogels. (f) The SEM image of patterned $\text{Ti}_3\text{C}_2\text{T}_x$ structure. (g) The proposed metal ionic cross-linking approach is capable of fabricating complex geometries, which are hard to achieve through other processing techniques. (e–g) Reproduced with permission.²³⁶ Copyright 2021, Wiley-VCH.

and catalysts.^{245–253} For instance, Xu *et al.*²⁵⁴ developed double-negative-index h-BN/graphene ceramic aerogels for thermal superinsulation under extreme conditions with ultra-low density down to $\sim 0.1 \text{ mg cm}^{-3}$ (Fig. 5e). In brief, they fabricated

graphene-based aerogels with hyperbolic architecture *via* a modified hydrothermal reduction and noncontact freeze-drying approach as a template. The attained porous aerogels were then used as templates to obtain h-BN aerogels through





Fig. 5 (a) Schematic illustration of ink fabrication and 3D printing of mixed-dimensional hybrid inks. (b) Optical image of a 3D-printed aerogel of GO with a toothed gear pattern. (c) A nonplanar geometry is prepared by printing MoS₂/GO hybrid ink. (d) The transmission electron microscopy (TEM) confirmed the bounding of MoS₂ in the cross-linked GO nanosheets. (a–d) Reproduced with permission.²⁴⁴ Copyright 2018, American Chemical Society. (e) The optical image of ultra-light h-BN aerogel resting on the stamen of a flower. (f) Schematic illustration of ultra-light h-BN aerogel fabrication through chemical vapor deposition of borazine on graphene aerogel template followed by thermal etching of graphene skeleton. (g and h) SEM images of the corresponding aerogel demonstrate (g) the double-pane wall structure caused by the thermal etching of graphene templates and (h) the microstructure of the h-BN aerogel. (e–h) Reproduced with permission.²⁵⁴ Copyright 2019, The American Association for the Advancement of Science.

chemical vapor deposition of borazine. Borazine was first self-condensed into polyborazylene and then polymerized into amorphous BN coating on a graphene aerogel template *via* dehydrogenation at 500 °C. Upon further annealing at 1500 °C, the amorphous BN crystallized into the highly ordered h-BN. Finally, the hybrid was annealed in air at 600 °C to etch the graphene template (Fig. 5f). Thermal etching of graphene templates formed a double-pane wall structure for h-BN aerogels. Benefiting from

the high bending stiffness of h-BN, the face-to-face collapse of these constructs was prevented, and the average gap size between the double-pane walls was controlled from a few to tens of nanometers (Fig. 5g and h). The corresponding h-BN aerogels exhibited exceptional mechanical and thermal characteristics with a negative Poisson's ratio of -0.25 and a negative linear thermal expansion coefficient of $-1.8 \times 10^{-6} \text{ } ^\circ\text{C}$. Furthermore, an elasticity of up to 95%, near-zero strength loss after sharp



thermal shocks, and ultra-low thermal conductivity in the vacuum of $\sim 20 \text{ mW m}^{-1} \text{ K}^{-1}$ were observed for this class of ceramic aerogels.

4. The marriage of 2D nanomaterial-based aerogels and PCMs

Encapsulating PCMs into multiscale supporting materials, also known as PCM confinement, revolutionized the development of multifunctional yet shape-stabilized thermal management systems.^{83,84,255} Depending on the dimensions of the supporting materials, confinement strategies are categorized into four subclasses, including core-shell (0D), longitudinal (1D), interface (2D), and porous (3D) confinements.⁸⁹ 0D confinement is defined as encapsulating PCMs with a protective layer through a core-shell structure, while 1D confinement is based on embedding PCMs into the inner cavity of nanofibrous materials such as CNTs. It is also possible to lock PCMs between the layers of various 2D nanomaterials, *e.g.*, graphene, MXene, and h-BN, through the interfacial interaction of the nanoparticles' surface and PCM molecules. Finally, in 3D confinement, aerogels are used as a template or holder to host PCMs in the interconnected nanoporous framework.⁸⁹ Aerogel confinement is proven to be one of the most effective ways to control the leakage of PCMs.⁸⁹ Besides, composite PCMs can inherit the inherent characteristics of their host and gain a second functionality (see Table 3 and the corresponding discussions in Sections 4-1 to 4-3). For example, composite PCMs of graphene or MXene can simultaneously showcase high electrical conductivity and unique thermal management characteristics, opening up numerous applications ranging from thermal management to EMI shielding.²⁵⁶⁻²⁶⁰

4.1. Graphene-based composite PCMs

Graphene-based aerogels, widely considered supporting materials, are a milestone in versatile advanced multifunctional composite PCMs with a higher thermal conductivity than pure PCMs. For example, Ye *et al.*²⁶¹ developed core-shell-like structured graphene/paraffin composite PCMs through a modified hydrothermal method. First, cyclohexane as a paraffin solvent was mixed to GO aqueous suspension to form a stable and homogenous graphene/paraffin emulsion. Next, graphene gels with micron-sized cyclohexane/paraffin droplet fillings were obtained after sequentially sealing the emulsion in Teflon autoclaves and heating it to 160 °C. The graphene-wrapped-cyclohexane hydrogels were then immersed in deionized water to remove the paraffin solvent and freeze-dried to fabricate a shape-stable composite PCM. The resultant composites are considered promising candidates for thermal energy storage systems, presenting an increase of 32% over the thermal conductivity of pure paraffin with a high paraffin encapsulation of 97 wt%, high enthalpy of 202.2 J g⁻¹, and freezing enthalpy of 213 J g⁻¹.

In another study, Wang *et al.*²⁶² introduced a programmable method to shape graphene/paraffin composites efficiently. In this regard, the ink-jetting coupled with liquid marbling and supercritical fluid drying approaches were used to develop

monodispersed graphene beads (Fig. 6a). Initially, uniform sol-gel droplets of GO/vitamin C with a narrow size distribution were fabricated through ink-jetting. Liquid marbling technology was then used to suppress the amalgamation and collision of the graphene-based droplets. Finally, the aerogel beads were prepared through CO₂ supercritical drying. A novel graphene-based composite PCM was obtained by capillary filling the aerogel beads with paraffin. The crystallinity, high latent heat, and high stability of PCMs were well maintained through these structures due to the existence of micro/nanopore channels of microsphere aerogels (Fig. 6b and c).

Interestingly, these micro-sphere composite PCMs were adopted into micro-circuits and were used as ultra-sensitive heat sensors with a detection limit of as low as 0.027 J. In a similar study, GO aerogel beads were developed through wet-spinning self-assembly of GO suspension into a coagulation bath containing 1 wt% polyethyleneimine (PEI) aqueous solution. The obtained graphene-based aerogel provided capillary forces and infiltration pathways for the impregnation of 1-tetradecanol (1-TD), *i.e.*, chemically pure paraffin. GO droplets were formed by extruding GO aqueous slurry *via* a syringe needle into a coagulation bath (Fig. 6d). The fabricated wet beads were then rinsed with deionized water, freeze-dried, and annealed at 110 °C to acquire reduced graphene beads (Fig. 6e and f). Finally, a composite PCM with a high latent heat of 232.2 J g⁻¹ was achieved by soaking the reduced aerogels in 1-TD. The thermal responsive tests of these composite PCMs before and after reduction are presented in Fig. 6g.²⁶³

Typically, the thermal conductivity of composite PCMs is expected to be amplified due to the PCM confinement. However, the considerable interfacial thermal resistance between graphene-based aerogels and PCMs can adversely affect the thermal conductivity of composite PCMs. In order to address this challenge, Mu and Li²⁶⁴ fabricated surface-modified graphene-based aerogels to diminish the interfacial thermal resistance between aerogels and PCMs. After adding vitamin C and/or EDA to the GO aqueous solution, a hydrogel was attained and freeze-dried to fabricate surface-modified graphene aerogel. Then, functionalized composite PCMs were obtained by infiltrating TD into the graphene/EDA and graphene/vitamin C interconnected network. Due to the uniform distribution of TD, the fabricated composite PCMs showcased unique stability with minimum PCM leakage.

High-temperature thermal annealing is another versatile approach to enhance the thermal conductivity of graphene-based composite PCMs without compromising the aerogels' features. For instance, Yang *et al.*⁶² developed a densely packed graphene aerogel by freeze-drying the molded GO paste with various architectures and annealing at 2800 °C. The fabricated aerogels were then infiltrated with 1-octadecanol (1-OC) to obtain shape-stable composite PCMs, even under simultaneous compressive force and thermal heating at 70 °C. Compared to the pristine PCM, the thermal conductivity and the latent heat of the as-made composite PCM enhanced up to 4.28 W m⁻¹ K⁻¹ (1760% higher than that of pure 1-OC) and $\sim 225 \text{ J g}^{-1}$, respectively.

Despite the progress discussed earlier with regard to graphene-based composite PCMs, their rigidity still hinders their potential for use in the thermal management of smart



Table 3 A library on 2D nanomaterial-based composite PCMs: form aerogel fabrication to thermal characteristics and adopted applications

Aerogel material	Aerogel fabrication process	Type of PCMs	PCM/aerogel composite				$\Delta H_m/\Delta H_f^e$ (J g ⁻¹)	Functionality	Ref.	
			PCM loading (wt%)	K_m^a (W m ⁻¹ K ⁻¹)	K_c^b (W m ⁻¹ K ⁻¹)	η^c (%)				T_m/T_f^d (°C)
rGO/expanded graphite	Hydrothermal reduction	Paraffin wax	92.42	0.2	0.79	295	52.9/46.2	210.6/207.2	Light-thermal energy storage	288
rGO/PAAS	Freeze-drying Directional freeze-casting	Paraffin wax	—	0.35	8.87/2.68	2434/665	—	179.0/—	Solar-thermal energy conversion	289
rGO	Thermal annealing Emulsification Chemical reduction	Paraffin wax	97	0.207	0.274	32	41.0/58.0	202.2/213.0	Thermal energy storage	261
rGO/CNTs	Freeze-drying Hydrothermal reduction	Paraffin wax	97.8	0.207	0.46	77	50.8/45.8	121.0/116.9	Solar-thermal energy conversion	290
rGO/CNTs	Freeze-drying Chemical-induced gelation	Paraffin wax	98.15	0.2	0.836	318	46.6/—	245.5/—	Thermal management	291
rGO	Freeze-drying Wet-spinning Freeze-drying	1-TD paraffin	99.83	—	—	—	40.0/—	232.2/228.4	Thermal energy storage Thermal management	263
rGO	Thermal annealing Chemical-induced gelation	<i>n</i> -Octadecane	96.7	0.15	0.47	215	35.1/13.8	195.7/196.7	Thermal energy storage	292
rGO/graphene nano-plates (GNPs)	Freeze-drying Thermal annealing Freeze-drying	PEG 10 000	97.75	0.31	1.43	361	64.8/41.8	185.6/177.8	Light-thermal energy conversion Energy storage Thermal management	293
rGO/CNTs	Chemical-induced gelation Freeze-drying	PEG 2000	98.79	0.227	0.76	235	53.8/—	162.2/—	Thermal management	294
rGO/lignin	Freeze-drying Chemical-induced gelation	PEG 4000	99.2	—	0.384	—	61.0/42.0	168.7/165.1	Solar-thermal energy conversion	295
GO	Freeze-drying Cross-linking	PEG 6000	99.5	0.211	0.344	63	42.0/61.0	218.9/213.2	Thermal energy storage	296
rGO/GNPs	Freeze-drying Hydrothermal reduction	1-OC	86.7	0.21	9.5	4423	62.0/48.53	196.2/234.1	Solar-thermal energy conversion Energy storage	297
rGO/GNPs	Air-drying Thermal annealing Hydrothermal reduction	1-OC	88	0.23	5.92	2473	59.0/53.9, 49.3	202.8/250.8	Thermal management Insulation	298
rGO	Air-drying Freeze-drying Thermal annealing	1-OC	95	0.23	4.28	1761	61.0/53.9	225.3/289.0	Thermal energy storage	62
rGO	Chemical-induced gelation	Lauric acid	94.31	0.267	1.207	352	43.3/40.6	207.3/205.8	Solar-thermal energy conversion	299
Carbonized GNPs/ CNFs/melamine foam	Freeze-drying Directional freeze-casting	Paraffin wax	95.9	0.28	1.42	407	52.4/46.3	154.3/159.7	Energy storage Solar-thermal energy conversion Electronic-thermal energy storage	300
rGO/TiO _{2-x}	Thermal annealing and carbonization Chemical-induced gelation	Paraffin wax	92.4	0.35	1.22	248	55.7/50.4	127.8/128.5	Photo-thermal conversion	301
rGO/GNPs	Freeze-drying Chemical vapor deposition of graphene on Ni/rGO foam	Paraffin wax	—	0.27	1.82	574	57.3/47.6	145.2/139.2	Light-thermal energy conversion Energy storage Solar energy conversion	302
rGO/Cu foam	Chemical Reduction	Paraffin wax	94.81	0.3	3.0	900	45.6/—	133.6/—	Solar energy conversion	303



Table 3 (continued)

Aerogel material	Aerogel fabrication process	Type of PCMs	PCM/aerogel composite					$\Delta H_m/\Delta H_f^e$ (J g ⁻¹)	Functionality	Ref.
			PCM loading (wt%)	K_m^a (W m ⁻¹ K ⁻¹)	K_c^b (W m ⁻¹ K ⁻¹)	η^c (%)	T_m/T_f^d (°C)			
rGO/poly(ethylene glycol)-grafted cellulose	Freeze-drying	PEG 6000	—	0.272	0.761	180	68.8/35.9	185.5/170.3	Energy storage	304
rGO	Chemical reduction Chemical-induced gelation Freeze-drying	Methoxy poly(ethylene glycol) mono-methacrylate (m-PEGMA) 1-TD	—	—	—	—	58.7/27.3	177.0/176.0	Thermal energy storage Solar-thermal-electric energy conversion	305
rGO/GNPs	Freeze-drying	1-TD	—	—	0.4069	—	42.87/30.3	213.7/212.4	Electrothermal energy harvesting	306
rGO/GNPs	Freeze-drying Chemical reduction	1-TD	—	0.0812	0.3408	320	44.68	220.4/213.6	Electrothermal energy harvesting	307
rGO	Ink jetting Liquid marbling Supercritical drying	Paraffin wax	91.3	—	—	—	47.8/—	136.6/144.4	Thermal Buffers Microelectronic devices	262
rGO/h-BN	BDFC Freeze-drying	PEG 10 000	88.35	0.3	2.94	880	—	145.5/—	Solar-thermal-electric energy conversion	281
rGO	Thermal annealing Chemical-induced gelation	1-TD	90	0.221	1.092	394	35.4/34.1	177.7/180.2	Thermal energy storage	264
rGO/konjac glucomannan	Freeze-drying Chemical-induced gelation	Sodium acetate tri-hydrate (SAT)	—	—	—	—	57.8/—	230.3/230.3	Solar-thermal energy conversion Energy storage	308
rGO/PVA/MMT nanosheets	Freeze-drying	Lauric acid	98.5	0.267	0.418	57	42.3/40.3	191.2/192.2	Solar-thermal energy conversion	309
rGO	Chemical-induced gelation Supercritical drying	Paraffin wax	94.8	—	—	—	—	—	Thermal energy storage	310
GNPs/cellulose	Chemical-induced gelation	PEG 6000	89.2	—	1.35	—	63.0/44.3	156.1/148.9	Thermal energy storage	311
rGO/BN nanotube	Freeze-drying Chemical-induced gelation	PEG 4000	98.5	0.29	0.43	48	59.1/38.5	195.6/175.9	Thermal management	312
rGO/scaphium scaphigerum	Freeze-drying Chemical-induced gelation	PEG 4000	—	0.28	1.15	311	63.0/43.8	164.2/140.6	Energy storage	313
rGO/CNTs	Freeze-drying Thermal annealing	Paraffin	98	0.2	2.182	991	48.1/—	222.1/—	—	314
rGO/BN	Chemical-induced gelation Freeze-drying	Paraffin	82.5	0.2782	1.68	504	54.1/47.4	123/—	Thermal energy storage Solar energy conversion	315
Graphite nanosheet/gelatin	Microwave reduction Freeze-casting Freeze-drying	Paraffin	> 93.2	0.264	3.75	1320	59.8/41.7	146.4/153.7	Building energy saving Human body hyperthermia Solar energy collection system	316
rGO/cellulose nanocrystals	Chemical-induced gelation Freeze-thawing Chemical reduction	PEG 6000	—	0.213	0.443	108	64.9/35.0	183.2/165.9	Energy storage	317
rGO/BN/melamine foam	Air-drying Chemical reduction Freeze-drying	PEG 6000	93.24	0.30	0.79	163	63.5/34.7	160.7/145.1	Thermal management component	318



Table 3 (continued)

Aerogel material	Aerogel fabrication process	Type of PCMs	PCM/aerogel composite				$\Delta H_m/\Delta H_f^e$ (J g ⁻¹)	Functionality	Ref.	
			PCM loading (wt%)	K_m^a (W m ⁻¹ K ⁻¹)	K_c^b (W m ⁻¹ K ⁻¹)	η^c (%)				T_m/T_f^d (°C)
Ti ₃ C ₂ T _x /gelatin	Freeze-drying	Paraffin wax	97.7	0.26	0.92	248	60.1/38.3	191.7/192.9	Thermoelectric devices under emergency conditions Solar-thermal energy storage	319
Ti ₃ C ₂ T _x	Freeze-drying	PEG 4000	95	—	—	—	57.5/33.8	112.3/108.5	Solar energy conversion	267
Ti ₃ C ₂ T _x	Freeze-drying	Phosphorus-modified stearyl alcohol	80	0.353	0.486	37	79.2/50.7	120.1/122.7	Energy storage Thermal insulation	266
Ti ₃ C ₂ T _x /polyimide	Freeze-drying	PEG 10 000	97.68	0.2109	0.3533	68	62.45/—	177.1/173.5	Solar-thermal energy storage Solar-thermal energy conversion	269
Ti ₃ C ₂ T _x /bacterial cellulose	Freeze-drying	Paraffin wax	88.56	—	—	—	23.42/19.2	89.02/93.49	Energy storage Photo-thermal energy conversion	273
Ti ₃ C ₂ T _x /bacterial cellulose	Chemical vapor deposition of MTMS Freeze-drying	PEG 4000	97.9	—	—	—	67.0/41.5	196.7/191.7	Photo-thermal conversion	320
Dopamine functionalized Ti ₃ C ₂ T _x /CNFs	Chemical-induced gelation	Erythritol	—	0.27	0.465	72	125.3/63.5	330.6/309.8	Energy storage Solar-thermal-electric energy conversion	268
Ti ₃ C ₂ T _x /Ni-platted/melamine sponge/GNPs/CNFs	Freeze-drying Freeze-drying Vacuum-assisted filtration	PEG 6000	99.61	0.27	0.48	78	63.0/38.9	154.3/150.3	EMI shield Thermal management	321
Ti ₃ C ₂ T _x /poly(3,4-ethylenedioxythiophene) polystyrene sulfonate (PEDOT:PSS) h-BN/CNFs	Freeze-casting Freeze-drying	PEG 20 000	98.78	0.3	0.36	20	61.6/46.9	237.6/236.1	EMI shield Thermal management	322
l-Glutamine grafted h-BN/CNFs	Freeze-drying	PEG 10 000	90	0.33	4.764	1344	60.2/41.6	136.8/122.8	Thermal insulation Solar-thermal energy storage	323
h-BN/CNFs/ Polyethyleneimine (PEI) MoS ₂ /MMT	Chemical-induced gelation Freeze-drying Chemical-induced gelation Freeze-drying Freeze-drying	PEG 4500 PEG 6000 Paraffin wax	— 95.6 —	0.28 0.28 —	0.59 0.4 —	110 43 —	42.3/15.2 57.2/34.2 41.3/43.4	143.5/136.1 165.3/169.3 151.7/145.8	Thermal energy storage Electric-thermal management Solar desalination	280 324 285
h-BN/chitosan	Freeze-drying	Paraffin wax	59	0.28	1.14	307	50.5/52.9	118.4/114.9	Electric-thermal energy storage	282
Biomass carbon	Freeze-drying Pyrolysis	Paraffin wax	95	0.248	0.427	72	63.5/54.5	83.6/98.8	Light-thermal energy conversion Energy storage	325

^a Thermal conductivity of PCM. ^b Thermal conductivity of aerogel-based composite PCM. ^c $\frac{k_{\text{aerogel/PCM}} - k_{\text{PCM}}}{k_{\text{PCM}}}$. ^d Melting temperature/freezing temperature. ^e Melting latent heat/freezing latent heat.





Fig. 6 (a) Schematic illustration of monodispersed graphene beads fabrication through ink-jetting coupled with liquid marbling and supercritical fluid drying. (b and c) SEM images of the fabricated (b) graphene-based aerogel microspheres and (c) the corresponding graphene/paraffin composites. (a–c) Reproduced with permission.²⁶² Copyright 2017, American Chemical Society (d) Schematic illustration of GO/1-TD composite PCM fabrication. (e and f) SEM images of (e) neat graphene beads and (f) the corresponding GO/1-TD composite PCMs. (g) Infrared thermal images of PDMS, 1-TD in PDMS, 1-TD/graphite in PDMS, 1-TD/GO, and 1-TD/rGO were placed on a hot plate. (d–g) Reproduced with permission.²⁶³ Copyright 2019, American Chemical Society.

flexible devices. To address this challenge, Sun *et al.*⁹⁹ have developed a novel flexible graphene/polyvinylidene fluoride-hexafluoropropylene (PVDF-HFP) aerogel-based composite phase change film. By introducing PVDF-HFP, the porous framework of graphene aerogel is strengthened, resulting in a superior flexible aerogel. Paraffin wax was impregnated into the supporting matrix to obtain the final phase change composite aerogels. The developed composite exhibited excellent thermal properties, long-term cycle stability, advanced flexibility, and outstanding solar-thermal conversion ability. The phase change enthalpy of this composite PCM reached 154.64 J g^{-1} and remained stable even after 500 heating-cooling cycles. The solar-thermal conversion efficiency of the developed composite PCMs was evaluated to be 95.98%, indicating a superior ability to convert solar energy into thermal energy. Interestingly, this

flexible graphene-based composite PCM was attached to a human model to demonstrate its advanced performance of wearable thermal management. Moreover, the excellent thermal energy storage capacity and solar-thermal conversion ability enable the graphene-based composite PCM to capture thermal heat from diverse energy sources. Therefore, this composite PCM has promising potential for broadening the application scenarios of advanced thermal energy management, not only for the intelligent temperature control equipment of the human body, but also for the thermal management of other complicated surfaces on controlled devices.

Shi *et al.*¹⁰⁰ also researched the development of mechanically robust and foldable graphene-based composite PCMs. To this end, the authors synthesized polyimide/graphene/ Fe_3O_4 hybrid aerogel films through a series of steps, including pre-polymerization, film



casting, freeze-drying, and thermal imidization. Subsequently, the researchers impregnated the aerogel framework with PEG as a PCM under a vacuum condition. The resulting hybrid aerogel films possessed ultra-light, foldable, and flexible characteristics. Furthermore, the hybrid aerogel films exhibited a high PEG loading of nearly 90 wt% due to their macroporous structure and large pore volume. The resultant hybrid aerogel/PEG composite films possessed good thermal management capability to regulate temperature through thermal energy absorption and release under a latent-heat capacity of over 158 J g^{-1} . More importantly, the multifunctional composite films displayed a wideband absorption capability at 7.0–16.5 GHz and a minimum reflection loss of -38.5 dB , resulting in excellent EM and infrared bi-stealth performance through the effective wideband microwave absorption of graphene/ Fe_3O_4 component and the thermal buffer of PEG.

4.2. MXene-based composite PCMs

MXene-based aerogels are fascinating supports for composite PCMs due to their exceptional electrical conductivity, high photothermal energy conversion efficiency, and acceptable thermal conductivity.^{89,265,266} Lin *et al.*²⁶⁷ introduced a sustainable and environmentally friendly fabrication strategy to establish MXene-based composite PCMs for solar-thermal energy management. In this work, MXene skeleton is considered a photothermal agent with high extinction coefficients in the ultraviolet-visible-near-infrared (UV-Vis-NIR) region, while PEG with high affinity to $\text{Ti}_3\text{C}_2\text{T}_x$ acts as a medium for thermal energy storage. The homogeneous $\text{Ti}_3\text{C}_2\text{T}_x$ /PEG dispersion was obtained by stirring, sealing, and heating the mixture of the PEG solution and $\text{Ti}_3\text{C}_2\text{T}_x$ colloid. Upon one-step freeze-drying, a binary $\text{Ti}_3\text{C}_2\text{T}_x$ -based composite PCM was fabricated, possessing a density of 30 mg cm^{-3} and a solar-thermal conversion efficiency of 92.5%.

In another study, Du *et al.*²⁶⁸ fabricated a novel biomass-derived composite PCM by impregnating sugar alcohol PCMs into MXene/CNFs aerogels. Selectively etching an aluminum layer of Ti_3AlC_2 followed by self-polymerization of dopamine on $\text{Ti}_3\text{C}_2\text{T}_x$ resulted in synthesizing 2D-layered polymerized dopamine-decorated nanosheets. A porous network was produced by sequential cation-induced gelation of the MXene/CNFs suspension and subsequent freeze-drying of the obtained hydrogel. The consequent aerogel loaded with erythritol, *i.e.*, sugar alcohol PCMs, to achieve a form-stable composite PCM offering solar-thermal-electricity conversion capacity with a maximum output voltage of 0.63 V. MXene-based composite PCMs were also used for solar-driven seawater desalination. First, as a water-soluble polyimide precursor, poly(amic acid) ammonium salt (PAAS) was synthesized through a polycondensation reaction. Then, by successive chemical reduction, freeze-drying, and thermal annealing, MXene/polyimide aerogels were fabricated and loaded with a high content of PEG, *i.e.*, up to 97.68 wt%. The as-fabricated composite PCMs exhibited a high enthalpy efficiency of up to 95.16%, an exceptional seawater evaporation mass of 6.07 kg m^{-2} , a high evaporation rate of $1.24 \text{ kg m}^{-2} \text{ h}^{-1}$ under one-sun illumination, and a high evaporation efficiency of 50.6%.²⁶⁹

A flame-retardant MXene-based composite PCM with high thermal stability was designed based on the chemical modification of stearyl alcohol (SAL) with a phosphorus-containing molecule. In this strategy, the MXene-based supporting skeleton was fabricated by freeze-casting and subsequent freeze-drying of $\text{Ti}_3\text{C}_2\text{T}_x$ suspensions. The flame-retardant composite PCMs were then made by a facile vacuum impregnation into the $\text{Ti}_3\text{C}_2\text{T}_x$ aerogels to hinder the PCM leakage. These flame-retardant and form-stable composite PCMs with a high thermal conductivity of $0.486 \text{ W m}^{-1} \text{ K}^{-1}$ PCM can potentially be used for solar energy storage applications.²⁶⁶

In another study, Cao *et al.*¹⁰¹ developed a multifunctional MXene-based composite PCM that exhibits excellent EMI shielding and efficient thermal energy management capabilities. This was achieved through the hybridization of cellulose nanocrystal/konjac glucomannan with intrinsically conductive $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets, followed by freeze-drying and thermal annealing. The resulting aerogels were then filled with paraffin wax using a vacuum impregnation method, which produced the aerogel-based phase change composites. The fabricated constructs exhibited notable reusable stabilities, excellent EMI shielding properties, and efficient thermal energy management capacities. For instance, the composite containing 2.3 wt% of $\text{Ti}_3\text{C}_2\text{T}_x$ demonstrated exceptional solar-thermal and electro-thermal conversion capabilities. Additionally, the EMI shielding effectiveness value was recorded at 45.0 dB (blocking more than 99.99% of unwanted electromagnetic noises), with a corresponding melting enthalpy value of 215.7 J g^{-1} (relative enthalpy efficiency of 99.9%). These findings suggest that the fabricated composite PCMs hold great potential for packaging sensitive electronics in the field of military and medical applications, due to their outstanding EMI shielding and advanced thermal energy management capabilities.^{270,271}

MXene-based composite PCMs have also been used as a promising solution for dual-camouflage under infrared/visible bands. To this end, Li *et al.*²⁷² have fabricated a trilayer composite that integrates key features such as thermal insulation, heat absorption, solar/electro-thermal conversions, and thermochromism. This innovative composite consists of an anisotropic $\text{Ti}_3\text{C}_2\text{T}_x$ /rGO hybrid aerogel, with n-octadecane PCM at the bottom and a thermochromic coating on the upper surface. By leveraging the heat insulation of the porous aerogel and the heat absorption capabilities of the PCM, the composite significantly minimizes the temperature difference between the human target and its surroundings to $0.9 \text{ }^\circ\text{C}$, providing infrared-stealth ability in low-temperature environments such as jungles and night conditions. Furthermore, it can conceal low-temperature object signals in the infrared image of high-temperature backgrounds and can be molded into a fake humanoid target with presupposed infrared characteristics to interfere with infrared detection. In addition, the composite adapts to varying environments by spontaneously increasing its surface temperature *via* solar-thermal conversion to around $50 \text{ }^\circ\text{C}$, thus altering its color from green to yellow in 30 seconds to match the ambient infrared characteristic and blend with the surrounding sandy color. This versatile and environmentally adaptable camouflage design holds



great promise for applications in daily thermal management and military protection.

In another intriguing study inspired by the smart thermal management of antifreeze beetles, Ji *et al.*²⁷³ devised composite PCM films by impregnating paraffin in a surface-modified MXene/bacterial-cellulose aerogel (Fig. 7). Antifreeze beetles have been blessed with a synergistic thermal regulation stemming from the light absorption of the black surfaces and the proteins' energy storage capability. In order to mimic this thermal

management behavior of antifreeze beetles, MXene/bacterial-cellulose hybrid aerogels were fabricated by freeze-drying the suspension of the exfoliated $Ti_3C_2T_x$ and bacterial-cellulose. The surface of the prepared aerogels was then modified through hydrophobic groups *via* chemical vapor deposition of methyltrimethoxysilane (MTMS). This surface modification approach not only strengthened the interaction between aerogel and PCMs but also prevented the leakage of liquid paraffin. Through forging and vacuum impregnation of PCMs into hydrophobic MXene-based

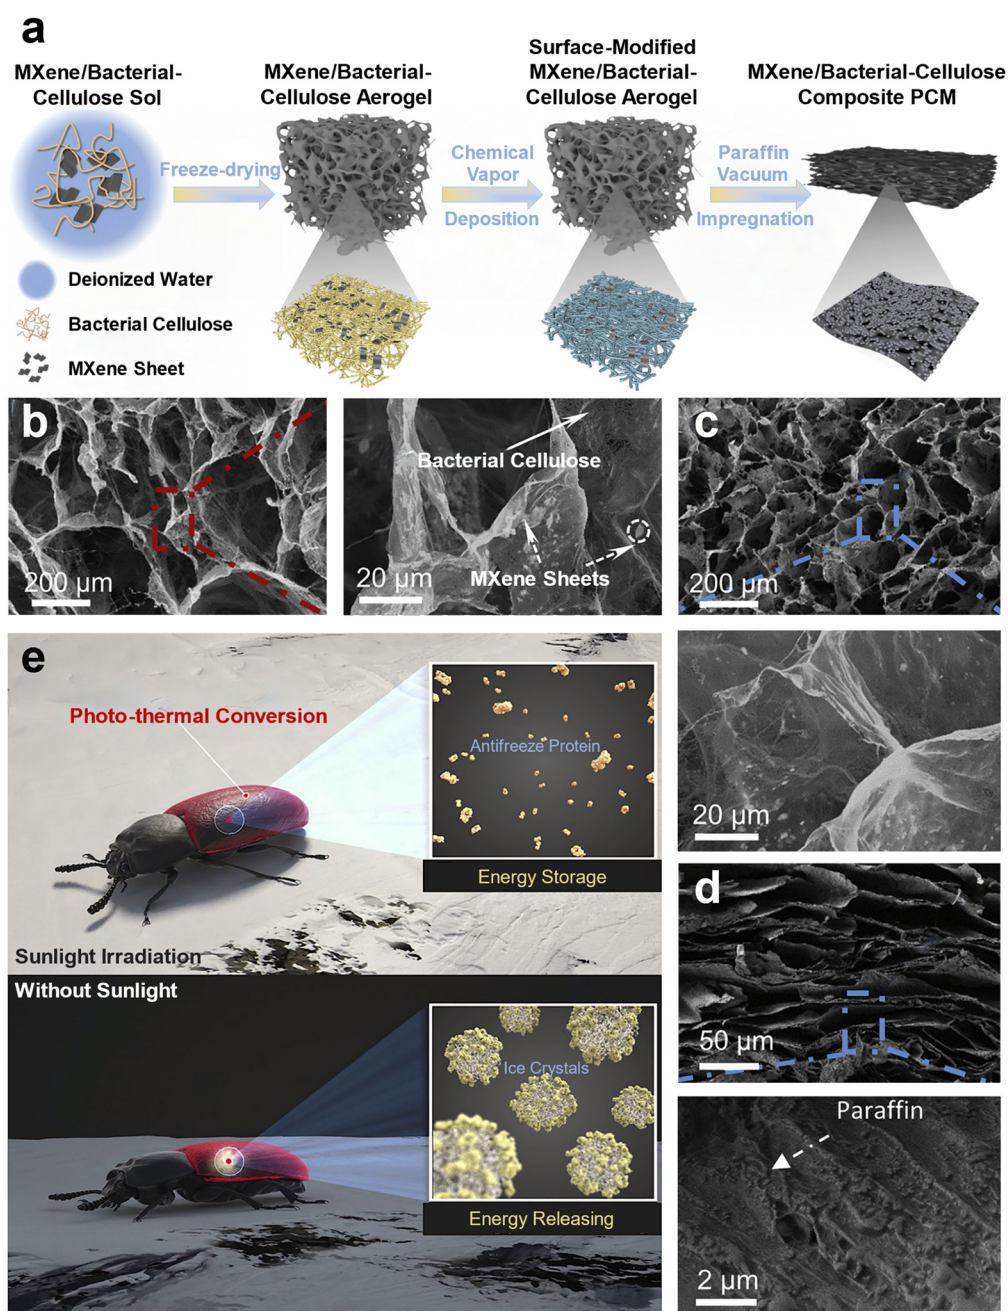


Fig. 7 (a) The preparation process of a surface-modified MXene/bacterial-cellulose aerogel-based composite PCM. (b–d) SEM images of (b) MXene/bacterial-cellulose aerogel, (c) the corresponding composite PCM, and (d) surface-modified MXene/bacterial-cellulose aerogel-based composite PCM. (e) Antifreeze beetles absorb sunlight energy through black spots and antifreeze proteins on their skins. This thermal energy will be released at night or in cold weather. Reproduced according to the terms of the Creative Commons CC-BY-NC-ND license.²⁷³ Copyright 2022, Elsevier.



supports, the MXene/bacterial-cellulose composite PCMs with super-lipophilic features were achieved. Finally, composite PCMs were compressed by a 5 kg weight to attain compact and laminated structures. Interestingly, the photothermal conversion of MXenes mimicked the black surface of beetles, while thermal storage through crystallization of PCMs resembled the energy storage of antifreeze proteins, resulting in bio-inspired thermal management systems.

4.3. Other 2D materials composite PCMs

Although a rapid heat transfer throughout composite PCMs is accomplished by adopting a highly thermally conductive network of either graphene-based or MXene-based aerogels, this concept could be applicable to aerogel-based composite PCMs of other 2D materials. The h-BN, so-called “white graphite”, with a similar structure to graphite, states high thermal conductivity, excellent electrical insulation properties, high thermal stability, and oxidation resistance, and therefore, has been used for developing advanced composite PCMs.^{274–279} For instance, a functionalized h-BN/CNFs composite PCM was reported to have 4.5 times higher thermal diffusivity than a pristine PEG, a high phase change enthalpy of 150.1 J g^{-1} , and excellent shape stability. In this work, an in-situ process was employed to functionalize h-BN nanosheets with hydroxyl and amino groups through ball-milling a mixture of L-glutamine and h-BN for 24 h. The L-glutamine-grafted h-BN/CNFs hydrogel was then formed by adding CNFs as the cross-linking agent to the suspension. The as-prepared hydrogel was freeze-dried to construct a robust and porous aerogel, which was then applied as a PEG 1500 confinement.²⁸⁰

The integration of h-BN composite PCMs with solar-thermoelectric generators was used to develop long-lasting energy generation systems for storing and converting clean solar energy. In this regard, a biomimetic aerogel of h-BN/GO, resembling the water-transportation microstructure of elaborate conifer trees, was designed through BDFC and used as a supporting skeleton for composite PCMs (Fig. 8a–f). The vacuum impregnation of 88.35 wt% PEG into these centrosymmetric and radially aligned aerogels led to the formation of high-performance composite PCMs for durable and real-environment solar-to-thermal/electric conversion with an effective photothermal energy conversion of $\sim 85.1\%$, an enhanced thermal conductivity of 880% over the thermal conductivity of pure PEG, and a high peak power density of 40.28 W m^{-2} .²⁸¹

Du *et al.*²⁸² also focused on degradable composite aerogels of h-BN as a substrate for stabilizing PCMs. The h-BN/chitosan suspensions were prepared by dispersing h-BN nanosheets in chitosan/acetic acid solution and poured into a Teflon mold. The resulting suspension was then freeze-dried to achieve a 3D aerogel framework with a well-preserved micro-structure. These aerogel templates were finally submerged into liquid paraffin to fabricate a thermally conductive h-BN/chitosan composite PCM. Since paraffin was impregnated into the aerogels by capillary forces and surface tensions, the resulting form-stable composite PCMs presented exceptionally stable thermo-physical

characteristics, *e.g.*, latent heat of 118.4 J g^{-1} and thermal conductivity of $1.14 \text{ W m}^{-1} \text{ K}^{-1}$.

In the context of cost-effective energy storage systems, MoS_2 is also becoming popular for aerogel-based composite PCMs due to its abundant resources and facile extraction. Besides, MoS_2 has significant solar absorbance in the infrared region owing to its high broadband antireflective characteristics.²⁸³ For instance, self-assembled 3D flower-like structures of MoS_2 nanosheets were reported to enhance the light-to-thermal conversion efficiency of 1-OC up to 85.5%.²⁸⁴

In an intriguing study, Gue *et al.*²⁸⁵ designed a bilayer aerogel system composed of MoS_2 and montmorillonite (MMT) integrated with PCMs for efficient solar energy harvesting and freshwater desalination. This system had two parts: (1) a bottom layer of MMT aerogel for water supply and thermal insulation, and (2) an upper layer of MoS_2 and paraffin/ SiO_2 aerogel-based phase change microcapsules for solar energy harvesting, storage, and steam generation (Fig. 8g–l). The composite PCMs have a latent heat of 177.85 J g^{-1} , allowing the system to store solar thermal energy during illumination and release heat for continuous seawater desalination during darkness. The results showed that the MoS_2 /MMT solar evaporator realized a water evaporation rate of $1.32 \text{ kg m}^{-2} \text{ h}^{-1}$ and an evaporation efficiency of 86.22% under a light intensity of 1 kW m^{-2} . Even when there was no sunlight, the evaporation rate and efficiency were still as high as $0.71 \text{ kg m}^{-2} \text{ h}^{-1}$ and 44.36% after 20 minutes of running.

Phosphorene (PR) nanoflakes are among other 2D nanomaterials used in developing high-performance aerogel-based composite PCMs. What sets PR nanoflakes apart is their unique properties, including a tunable bandgap, high charge mobility, and excellent biocompatibility.^{56,286} Their anisotropic orthorhombic structure means that they are ductile along one of the in-plane crystal directions but stiff along the other.^{56,286} This property gives them unusual mechanical, electronic, optical, and transport properties that reflect the anisotropy of the lattice. PR nanoflakes also exhibit superior photothermal conversion efficiency near-infrared light, rendering them very promising for photothermal utilization. Therefore, incorporating PR nanoflakes into aerogel-based composite PCMs can enhance the mechanical performance of the hybrid aerogel through a nanoscale reinforcement effect, as well as promote external heat transfer through enhanced infrared photothermal conversion from a high-temperature target. To this end, Shi *et al.*⁵⁶ developed flexible and foldable composite films based on polyimide/PR hybrid aerogel and PCMs for infrared stealth and thermal camouflage applications. The composite films were obtained by fabricating a polyimide/PR hybrid aerogel through prepolymerization, film casting, freeze-drying, and thermal imidization, followed by vacuum impregnation of PEG as a PCM into the aerogel framework. The combination of polyimide and PR nanoflakes endows the hybrid aerogels an effective enhancement in mechanical properties, near infrared absorption, and infrared photothermal conversion. The resultant composite films not only present prominent tensile and fatigue-resistant performance but also exhibit good thermal regulation capability with a high latent-heat capacity of over 150 J g^{-1} . Moreover, the composite films demonstrate good infrared stealth





Fig. 8 (a) Schematic illustration of BDFC approach for preparing bioinspired h-BN/GO aerogel. (b) Vertically and (c) radially aligned channels of the water transportation system within towering conifer trees. (d) Optical images of h-BN/GO aerogel. (e) Cross-sectional morphology of the corresponding aerogel. (f) Schematic and SEM images of the cross-sectional and longitudinal section of the h-BN/GO scaffold before and after PCM impregnation. (a–f) Reproduced with permission,²⁸¹ Copyright 2020, American Chemical Society. (g–i) Optical images of bilayer aerogel systems. (j–l) SEM images of (j) MoS₂ and (k) paraffin/SiO₂ aerogel-based phase change microcapsules and (l) MMT aerogels. (g–l) Reproduced with permission,²⁸⁵ Copyright 2022, Elsevier.

and thermal camouflage performance on high-temperature targets through effective thermal buffer and insulation.

Zheng *et al.*²⁸⁷ also developed composites of PCMs and PR nanosheets for efficient solar energy capture and photothermal conversion. The composite was basically made of polyimide/PR hybrid aerogels and PEG as the PCM. The synthesis involved the fabrication of a series of hybrid aerogels by incorporating different loadings of PR nanosheets into polyimide using freeze-drying and thermal imidization techniques. The resulting hybrid aerogels were then impregnated with PEG through

vacuum impregnation to create the composite PCMs. The introduction of PR nanosheets increased the volume capacity of the hybrid aerogels, leading to a remarkable improvement in the loading amount of PEG. Interestingly, the hybrid aerogels displayed a lightweight nature with a density of 21.9 mg cm⁻³ when 16 wt% of PR nanosheets were incorporated. This resulted in an extremely high PEG loading of 4067% in the aerogel system. Additionally, the incorporation of PR nanosheets into the polyimide matrix enhanced solar light absorption and photothermal energy conversion for the hybrid aerogel/PEG



composites. The resulting hybrid aerogel/PEG composites exhibited a high latent-heat capacity of over 170 J g^{-1} and a high photothermal conversion efficiency of 82.5%. Moreover, the composites demonstrated good thermal impact resistance by retaining their original shape and form even after heating at $80 \text{ }^\circ\text{C}$ for 20 min. Furthermore, the composite PCMs maintained high thermal cycle stability after thermal cycling 500 times.

5. Current challenges and future prospects

The future of aerogel-based composite PCMs seems to be boundless in thermal management systems, mainly due to their form stability and enhanced thermal conductivity compared to pure PCMs. These unique characteristics of composite PCMs are influenced by their supporting scaffolds. In this regard, we have reviewed various methods for aerogel fabrication, including drying approaches and pre-treatment methods, as well as advances in 2D nanomaterial-based aerogels and their potential uses in composite PCMs. Additionally, we have discussed the versatile advances proposed in 2D nanomaterial aerogel-based composite PCMs, specifically focusing on the type and functionality of the scaffolds.

Despite these advancements, large-scale fabrication of aerogels yet remains a challenge for practical applications in both industrial and domestic settings. The study presented by Yang *et al.*¹⁷⁴ on scalable fabrication ($\sim 1 \text{ m}^2$) of structure-intact graphene-based aerogels through simple freezing and air-drying of chemically reduced foam-like GO suspension has the potential to address this challenge. However, such a scalable process is yet to be explored for cost-effective aerogel-based composite PCMs. On the other hand, mechanical robustness and flexibility are among the other core challenges of aerogel-based composite PCMs. Up to now, the research on flexible and foldable composite PCMs has been limited, with only a few studies, such as Sun *et al.*⁹⁹ (flexible graphene/PVDFHFP aerogel-based composite PCMs) and Shi *et al.*⁵⁶ (flexible and foldable polyimide/PR hybrid aerogel-based composite PCMs), attempting to address the challenges in this area. As such, there is a significant need for further exploration of flexible and foldable composite PCMs, as they represent an important research topic in this field. All in all, if composite PCMs become flexible, a myriad of applications, from wearable heat sensors to thermal resistance clothing, can be added to PCM-based thermal management systems.

Expanding the range of applications for aerogel-based composite PCMs is an area that requires further research. Currently, most studies on these materials focus primarily on thermal management systems and related topics, such as solar desalination and photo-thermal energy conversion. However, the functionality of the aerogel-based scaffolds is not fully adopted in composite PCMs. The study by Zhao *et al.*,²⁶³ which used aerogel-based composite PCMs of graphene for thermal management and heat sensing, is one of the rare examples of utilizing the functionality of aerogel-based scaffolds in the final composite PCMs. In this regard, we can also refer to the work of Shi *et al.*,¹⁰⁰ where a polyimide/graphene/ Fe_3O_4 hybrid aerogel

was used as a skeleton to produce multifunctional composite PCMs with simultaneous EMI and infrared shielding capabilities. All in all, we expect that future studies will follow a similar trend to take advantage of the inherent functionalities of aerogel skeletons and achieve multi-responsive and multifunctional composite PCMs with novel characteristics.

Last but not least, there is no in-depth comparative investigation on the phase transition enthalpy, specific heat, expansion coefficient, and energy storage capacity of various 2D aerogel-based composite PCMs. Such a perspective regarding these heat transfer mechanisms is crucial to select the best candidate for the large-scale fabrication of composite PCMs. Additionally, it is important to investigate the pros and cons of various 2D aerogel scaffolds before using them for composite PCMs. For example, MXenes showcase great excellent water processability, electrical conductivity, and thermal characteristics, which are necessary for developing multifunctional thermal management composites. However, this class of 2D nanomaterials is susceptible to oxidation and thermal degradations.³²⁶ Therefore, it is necessary to investigate the long-term effects of these shortcomings on the overall performance of MXene-based composite PCMs to ensure their suitability for practical applications.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledge the Syilx Okanagan Nation for the use of their traditional, ancestral, and unceded territory, the land on which the research was conducted. The authors acknowledge the support of the Natural Sciences and Engineering Research Council of Canada (NSERC) [funding reference number ALLRP 555586-20]. Dr Arjmand appreciate the financial support provided by the University of British Columbia (UBC), the Canada Research Chairs Program, and Zentek Ltd.

References

- 1 R. Gulfam, P. Zhang and Z. Meng, *Appl. Energy*, 2019, **238**, 582–611.
- 2 B. Zhao, R. Zhu, N. Sheng, C. Zhu and Z. Rao, *Energy Fuels*, 2022, **36**, 10354–10363.
- 3 X. Min, B. Sun, S. Chen, M. Fang, X. Wu, Y. G. Liu, A. Abdelkader, Z. Huang, T. Liu, K. Xi and R. Vasant Kumar, *Energy Storage Mater.*, 2019, **16**, 597–606.
- 4 Y. Zhao, X. Min, Z. Ding, S. Chen, C. Ai, Z. Liu, T. Yang, X. Wu, Y. G. Liu, S. Lin, Z. Huang, P. Gao, H. Wu and M. Fang, *Adv. Sci.*, 2020, **7**, 1902051.
- 5 D. Lencer, M. Salina and M. Wuttig, *Adv. Mater.*, 2011, **23**, 2030–2058.
- 6 K. Pielichowska and K. Pielichowski, *Prog. Mater. Sci.*, 2014, **65**, 67–123.



- 7 M. Wuttig, H. Bhaskaran and T. Taubner, *Nat. Photonics*, 2017, **11**, 465–476.
- 8 Z. Zhu, P. G. Evans, R. F. Haglund, Jr. and J. G. Valentine, *Nano Lett.*, 2017, **17**, 4881–4885.
- 9 P. Lian, R. Yan, Z. Wu, Z. Wang, Y. Chen, L. Zhang and X. Sheng, *Adv. Compos. Hybrid Mater.*, 2023, **6**, 74.
- 10 J.-F. Su, X.-Y. Wang, S. Han, X.-L. Zhang, Y.-D. Guo, Y.-Y. Wang, Y.-Q. Tan, N.-X. Han and W. Li, *J. Mater. Chem. A*, 2017, **5**, 23937–23951.
- 11 L. Yang, X. Jin, Y. Zhang and K. Du, *J. Cleaner Prod.*, 2021, **287**, 124432.
- 12 E. Zdraveva, J. Fang, B. Mijovic and T. Lin, *Ind. Eng. Chem. Res.*, 2015, **54**, 8706–8712.
- 13 J. T. McCann, M. Marquez and Y. Xia, *Nano Lett.*, 2006, **6**, 2868–2872.
- 14 R. K. Sharma, P. Ganesan, V. V. Tyagi, H. S. C. Metselaar and S. C. Sandaran, *Energy Convers. Manage.*, 2015, **95**, 193–228.
- 15 Y. Yuan, N. Zhang, W. Tao, X. Cao and Y. He, *Renewable Sustainable Energy Rev.*, 2014, **29**, 482–498.
- 16 A. Fallahi, G. Guldentops, M. Tao, S. Granados-Focil and S. Van Dessel, *Appl. Therm. Eng.*, 2017, **127**, 1427–1441.
- 17 H. Ke, *Sol. Energy*, 2018, **173**, 1197–1206.
- 18 Y. Ueki, H. Murashima and M. Shibahara, *Int. J. Heat Mass Transfer*, 2020, **163**, 120463.
- 19 R. Shen, L. Liu, Y. Cao, L. Zhang, X. Sheng and Y. Chen, *Sol. Energy*, 2022, **242**, 287–297.
- 20 C. Liu, F. Li, L. P. Ma and H. M. Cheng, *Adv. Mater.*, 2010, **22**, E28–62.
- 21 M. Graham, J. A. Coca-Clemente, E. Shchukina and D. Shchukin, *J. Mater. Chem. A*, 2017, **5**, 13683–13691.
- 22 K. Kant, A. Shukla and A. Sharma, *Sol. Energy Mater.*, 2017, **172**, 82–92.
- 23 X. Chen, P. Cheng, Z. Tang, X. Xu, H. Gao and G. Wang, *Adv. Sci.*, 2021, **8**, 2001274.
- 24 C. Amaral, R. Vicente, P. A. A. P. Marques and A. Barros-Timmons, *Renewable Sustainable Energy Rev.*, 2017, **79**, 1212–1228.
- 25 M. M. Joybari, F. Haghighat and S. Seddegh, *Sol. Energy*, 2017, **158**, 711–720.
- 26 S. A. Mohamed, F. A. Al-Sulaiman, N. I. Ibrahim, M. H. Zahir, A. Al-Ahmed, R. Saidur, B. S. Yilbaş and A. Z. Sahin, *Renewable Sustainable Energy Rev.*, 2017, **70**, 1072–1089.
- 27 A. Chibani, S. Merouani, F. Benmoussa, M. H. Abdellattif, A. Erto, B.-H. Jeon and Y. Benguerba, *J. Environ. Chem. Eng.*, 2021, **9**, 106744.
- 28 Y. Lin, Y. Jia, G. Alva and G. Fang, *Renewable Sustainable Energy Rev.*, 2018, **82**, 2730–2742.
- 29 P. Manoj Kumar, D. Sudarvizhi, P. M. J. Stalin, A. Aarif, R. Abhinandhana, A. Renuprasanth, V. Sathya and N. T. Ezhilan, *Mater. Today: Proc.*, 2021, **45**, 7876–7880.
- 30 M. A. Sheik, M. K. Aravindan, N. Beemkumar, P. K. Chaurasiya and J. A. Dhanraj, *Arabian J. Sci. Eng.*, 2022, **47**, 15899–15913.
- 31 S. Song, F. Qiu, W. Zhu, Y. Guo, Y. Zhang, Y. Ju, R. Feng, Y. Liu, Z. Chen, J. Zhou, C. Xiong and L. Dong, *Sol. Energy Mater.*, 2019, **193**, 237–245.
- 32 J. Chen, Z. Mo, Y. Chen, P. Mo, Z. Hu, X. Chen, J. Yu, Z. Hao, X. Zeng, R. Sun and J. Xu, *ACS Appl. Energy Mater.*, 2022, **5**, 11669–11683.
- 33 S. Chen, A. L. Moore, W. Cai, J. W. Suk, J. An, C. Mishra, C. Amos, C. W. Magnuson, J. Kang, L. Shi and R. S. Ruoff, *ACS Nano*, 2011, **5**, 321–328.
- 34 M. Li and B. Mu, *Appl. Energy*, 2019, **242**, 695–715.
- 35 Y. He, H. Li, F. Luo, Y. Jin, B. Huang and Q. Qian, *Composites, Part A*, 2021, **151**, 106638.
- 36 H. Liu, Z. Han, Q. Wang, X. Wang, D. Wu and X. Wang, *Appl. Surf. Sci.*, 2021, **562**, 150211.
- 37 Z. Sun, H. Liu and X. Wang, *Composites, Part B*, 2022, **242**, 110112.
- 38 H. Liu, X. Tian, M. Ouyang, X. Wang, D. Wu and X. Wang, *Renewable Energy*, 2021, **179**, 47–64.
- 39 H. Liu, X. Wang and D. Wu, *Sustainable Energy Fuels*, 2019, **3**, 1091–1149.
- 40 M. Graham, E. Shchukina, P. F. De Castro and D. Shchukin, *J. Mater. Chem. A*, 2016, **4**, 16906–16912.
- 41 Y. Konuklu, H. O. Paksoy and M. Unal, *Appl. Energy*, 2015, **150**, 335–340.
- 42 A. Sari, C. Alkan and C. Bilgin, *Appl. Energy*, 2014, **136**, 217–227.
- 43 A. Sari, C. Alkan, D. Kahraman Döğüşcü and A. Biçer, *Sol. Energy Mater.*, 2014, **126**, 42–50.
- 44 P. Singh, R. K. Sharma, M. Khalid, R. Goyal, A. Sari and V. V. Tyagi, *Sol. Energy Mater.*, 2022, **246**, 111896.
- 45 D. G. Atinafu, B. Y. Yun, S. Yang, H. Yuk, S. Wi and S. Kim, *Energy Storage Mater.*, 2021, **42**, 164–184.
- 46 R. Ye, H. Jiang, J. Wang, X. Yang and X. Shu, *Sol. Energy Mater.*, 2022, **238**, 111584.
- 47 H. Liu, Z. Zheng, Z. Qian, Q. Wang, D. Wu and X. Wang, *Sol. Energy Mater.*, 2021, **229**, 111140.
- 48 R. Chatterjee, D. Beysens and S. Anand, *Adv. Mater.*, 2019, **31**, e1807812.
- 49 A. L. Cottrill, A. T. Liu, Y. Kunai, V. B. Koman, A. Kaplan, S. G. Mahajan, P. Liu, A. R. Toland and M. S. Strano, *Nat. Commun.*, 2018, **9**, 664.
- 50 C. Liu, J. Zhang, J. Liu, Z. Tan, Y. Cao, X. Li and Z. Rao, *Angew. Chem., Int. Ed.*, 2021, **60**, 13978–13987.
- 51 S. Zhang, Q. Li, N. Yang, Y. Shi, W. Ge, W. Wang, W. Huang, X. Song and X. Dong, *Adv. Funct. Mater.*, 2019, **29**, 1906805.
- 52 X. Chen, H. Gao, Z. Tang and G. Wang, *Cell Rep. Phys. Sci.*, 2020, **1**, 100218.
- 53 Y. Cai, Q. Wei, F. Huang, S. Lin, F. Chen and W. Gao, *Renew. Energy*, 2009, **34**, 2117–2123.
- 54 E. Pakdel, M. Naebe, L. Sun and X. Wang, *ACS Appl. Mater. Interfaces*, 2019, **11**, 13039–13057.
- 55 J. Shi, M. Qin, W. Aftab and R. Zou, *Energy Storage Mater.*, 2021, **41**, 321–342.
- 56 T. Shi, Z. Zheng, H. Liu, D. Wu and X. Wang, *Compos. Sci. Technol.*, 2022, **217**, 109127.
- 57 Z. Tao, X. Chen, M. Yang, X. Xu, Y. Sun, Y. Li, J. Wang and G. Wang, *Sol. Energy Mater.*, 2020, **215**, 110600.
- 58 H. Fang, J. Lin, L. Zhang, A. Chen, F. Wu, L. Geng and X. Peng, *Carbohydr. Polym.*, 2020, **249**, 116836.



- 59 X. Liu and Z. Rao, *J. Energy Storage*, 2020, **32**, 101860.
- 60 R. Shen, M. Weng, L. Zhang, J. Huang and X. Sheng, *Composites, Part A*, 2022, **163**, 107248.
- 61 P. Min, J. Liu, X. Li, F. An, P. Liu, Y. Shen, N. Koratkar and Z.-Z. Yu, *Adv. Funct. Mater.*, 2018, **28**, 1805365.
- 62 J. Yang, X. Li, S. Han, R. Yang, P. Min and Z.-Z. Yu, *J. Mater. Chem. A*, 2018, **6**, 5880–5886.
- 63 S. Wang, K. Lei, Z. Wang, H. Wang and D. Zou, *Chem. Eng. J.*, 2022, **438**, 135559.
- 64 M. Yadav, N. Pasarkar, A. Naikwadi and P. Mahanwar, *Polym. Bull.*, 2022, 1–31.
- 65 D. He and M. H. M. Isa, *Adv. Civ. Eng. Mater.*, 2023, **310**, DOI: [10.1007/978-981-19-8024-4_20](https://doi.org/10.1007/978-981-19-8024-4_20).
- 66 M. Pomianowski, P. Heiselberg and Y. Zhang, *Energy Build.*, 2013, **67**, 56–69.
- 67 L. F. Cabeza, A. Castell, C. D. Barreneche, A. De Gracia and A. Fernández, *Renewable Sustainable Energy Rev.*, 2011, **15**, 1675–1695.
- 68 P. K. Kushwaha, N. K. Sharma, A. Kumar and C. S. Meena, *Buildings*, 2023, **13**, 79.
- 69 S. Chandel and T. Agarwal, *Renewable Sustainable Energy Rev.*, 2017, **67**, 581–596.
- 70 R. Sharma, P. Ganesan, V. Tyagi, H. Metselaar and S. Sandaran, *Energy Convers. Manage.*, 2015, **95**, 193–228.
- 71 X. Chen, P. Cheng, Z. Tang, X. Xu, H. Gao and G. Wang, *Adv. Sci.*, 2021, **8**, 2001274.
- 72 Y. Tao, C. Lin and Y. He, *Energy Convers. Manage.*, 2015, **97**, 103–110.
- 73 C. Li, Q. Li and Y. Ding, *Appl. Energy*, 2019, **247**, 374–388.
- 74 A. C. Evers, M. A. Medina and Y. Fang, *Build. Environ.*, 2010, **45**, 1762–1768.
- 75 A. Sangeetha, S. Shanmugan, A. J. Alrubaie, M. M. Jaber, H. Panchal, M. E. H. Attia, A. H. Elsheikh, D. Mevada and F. A. Essa, *Desalination*, 2023, **551**, 116367.
- 76 S. Rostami, M. Afrand, A. Shahsavari, M. Sheikholeslami, R. Kalbasi, S. Aghakhani, M. S. Shadloo and H. F. Oztop, *Energy*, 2020, **211**, 118698.
- 77 F. Javadi, H. Metselaar and P. Ganesan, *Sol. Energy*, 2020, **206**, 330–352.
- 78 R. Raud, R. Jacob, F. Bruno, G. Will and T. A. Steinberg, *Renewable Sustainable Energy Rev.*, 2017, **70**, 936–944.
- 79 E. Van Artsdalen and I. Yaffe, *J. Phys. Chem.*, 1955, **59**, 118–127.
- 80 R. DiGiulio and A. S. Teja, *Int. J. Thermophys.*, 1992, **13**, 855–871.
- 81 R. Parameshwaran, K. Deepak, R. Saravanan and S. Kalaiselvam, *Appl. Energy*, 2014, **115**, 320–330.
- 82 A. Pasupathy, R. Velraj and R. Seeniraj, *Renewable Sustainable Energy Rev.*, 2008, **12**, 39–64.
- 83 M.-H. Sun, S.-Z. Huang, L.-H. Chen, Y. Li, X.-Y. Yang, Z.-Y. Yuan and B.-L. Su, *Chem. Soc. Rev.*, 2016, **45**, 3479–3563.
- 84 M. M. Umair, Y. Zhang, K. Iqbal, S. Zhang and B. Tang, *Appl. Energy*, 2019, **235**, 846–873.
- 85 M. Wu, S. Wu, Y. Cai, R. Wang and T. Li, *Energy Storage Mater.*, 2021, **42**, 380–417.
- 86 Y. Konuklu, H. O. Paksoy and M. Unal, *Appl. Energy*, 2015, **150**, 335–340.
- 87 A. Sari, C. Alkan and C. Bilgin, *Appl. Energy*, 2014, **136**, 217–227.
- 88 A. Sari, C. Alkan, D. K. Döğüşcü and A. Biçer, *Solar Energy Mater. Solar Cells*, 2014, **126**, 42–50.
- 89 P. Liu, X. Chen, Y. Li, P. Cheng, Z. Tang, J. Lv, W. Aftab and G. Wang, *ACS Nano*, 2022, **16**, 15586–15626.
- 90 J. Zhang, S. Wang, S. Zhang, Q. Tao, L. Pan, Z. Wang, Z. Zhang, Y. Lei, S. Yang and H. Zhao, *J. Phys. Chem. C*, 2011, **115**, 20061–20066.
- 91 Y. Zhu, S. Liang, K. Chen, X. Gao, P. Chang, C. Tian, J. Wang and Y. Huang, *Energy Convers. Manage.*, 2015, **105**, 908–917.
- 92 S. Zhang, S. Wang, J. Zhang, Y. Jiang, Q. Ji, Z. Zhang and Z. Wang, *J. Phys. Chem. C*, 2013, **117**, 23412–23417.
- 93 L. Pan, Q. Tao, S. Zhang, S. Wang, J. Zhang, S. Wang, Z. Wang and Z. Zhang, *Sol. Energy Mater.*, 2012, **98**, 66–70.
- 94 H. Luo, Y. Huang, D. Wang and J. Shi, *J. Polym. Sci., Part B: Polym. Phys.*, 2013, **51**, 376–383.
- 95 S. Sinha-Ray, R. Sahu and A. Yarin, *Soft Matter*, 2011, **7**, 8823–8827.
- 96 C. Nie, X. Tong, S. Wu, S. Gong and D. Peng, *RSC Adv.*, 2015, **5**, 92812–92817.
- 97 S. Zhang, Q. Tao, Z. Wang and Z. Zhang, *J. Mater. Chem.*, 2012, **22**, 20166–20169.
- 98 B. Yang, T. Zhang, J. Wang, J. Lv, Y. Zheng, Y. Zhang and Y. Wang, *Sol. Energy Mater.*, 2022, **247**, 111948.
- 99 K. Sun, H. Dong, Y. Kou, H. Yang, H. Liu, Y. Li and Q. Shi, *Chem. Eng. J.*, 2021, **419**, 129637.
- 100 T. Shi, Z. Zheng, H. Liu, D. Wu and X. Wang, *Nanomaterials*, 2021, **11**, 3038.
- 101 Y. Cao, Z. Zeng, D. Huang, Y. Chen, L. Zhang and X. Sheng, *Nano Res.*, 2022, **15**, 8524–8535.
- 102 S. S. Kistler, *Nature*, 1931, **127**, 741.
- 103 J. P. Vareda, A. Lamy-Mendes and L. Durães, *Microporous Mesoporous Mater.*, 2018, **258**, 211–216.
- 104 M. A. Aegerter, N. Leventis and M. Koebel, *Aerogels Handbook*, Springer, New York, NY, USA, 2011.
- 105 B. Liu, J. Zhuang and G. Wei, *Environ. Sci.: Nano*, 2020, **7**, 2195–2213.
- 106 D. Zhu, B. Liu and G. Wei, *Biosensors*, 2021, **11**, 259.
- 107 P. Gupta, B. Singh, A. K. Agrawal and P. K. Maji, *Mater. Des.*, 2018, **158**, 224–236.
- 108 H. Kong, Y. Chen, G. Yang, B. Liu, L. Guo, Y. Wang, X. Zhou and G. Wei, *Nanoscale Horiz.*, 2022, **7**, 112–140.
- 109 D. M. Smith, A. Maskara and U. Boes, *J. Non-Cryst. Solids*, 1998, **225**, 254–259.
- 110 A. A. Balandin, *Nat. Mater.*, 2011, **10**, 569–581.
- 111 D. L. Nika and A. A. Balandin, *J. Phys. Condens.*, 2012, **24**, 233203.
- 112 K. S. Novoselov, A. K. Geim, S. V. Morozov, D.-E. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, *Science*, 2004, **306**, 666–669.
- 113 D. Golberg, Y. Bando, Y. Huang, T. Terao, M. Mitome, C. Tang and C. Zhi, *ACS Nano*, 2010, **4**, 2979–2993.
- 114 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, *Nat. Nanotechnol.*, 2011, **6**, 147–150.



- 115 X. Zhang, R. Lv, A. Wang, W. Guo, X. Liu and J. Luo, *Angew. Chem.*, 2018, **130**, 15248–15253.
- 116 Y.-M. Lin, C. Dimitrakopoulos, K. A. Jenkins, D. B. Farmer, H.-Y. Chiu, A. Grill and P. Avouris, *Science*, 2010, **327**, 662.
- 117 T. Mueller, F. Xia and P. Avouris, *Nat. Photonics*, 2010, **4**, 297–301.
- 118 A. Pospischil, M. M. Furchi and T. Mueller, *Nat. Nanotechnol.*, 2014, **9**, 257–261.
- 119 X. Yang, C. Cheng, Y. Wang, L. Qiu and D. Li, *Science*, 2013, **341**, 534–537.
- 120 Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong and H. Dai, *J. Am. Chem. Soc.*, 2011, **133**, 7296–7299.
- 121 B. Liu, L. Chen, G. Liu, A. N. Abbas, M. Fathi and C. Zhou, *ACS Nano*, 2014, **8**, 5304–5314.
- 122 K. Raagulan, B. M. Kim and K. Y. Chai, *Nanomaterials*, 2020, **10**, 702.
- 123 M. Kamkar, A. Ghaffarkhah, R. Ajdary, Y. Lu, F. Ahmadijokani, S. E. Mhatre, E. Erfanian, U. Sundararaj, M. Arjmand and O. J. Rojas, *Small*, 2022, **2200220**.
- 124 S. A. Hashemi, A. Ghaffarkhah, E. Hosseini, S. Bahrani, P. Najmi, N. Omidifar, S. M. Mousavi, M. Amini, M. Ghaedi and S. Ramakrishna, *Matter*, 2022, **5**, 3807–3868.
- 125 N. Howe and S. Bundell, *Nature*, 2020, DOI: [10.1038/d41586-020-02448-5](https://doi.org/10.1038/d41586-020-02448-5).
- 126 R.-L. Liu, W.-J. Ji, T. He, Z.-Q. Zhang, J. Zhang and F.-Q. Dang, *Carbon*, 2014, **76**, 84–95.
- 127 X. Fu, J.-Y. Choi, P. Zamani, G. Jiang, M. A. Hoque, F. M. Hassan and Z. Chen, *ACS Appl. Mater. Interfaces*, 2016, **8**, 6488–6495.
- 128 X. Huang, X. Chen, A. Li, D. Atinafu, H. Gao, W. Dong and G. Wang, *Chem. Eng. J.*, 2019, **356**, 641–661.
- 129 Y. Li, X. Huang, G. Hai, J. Lv, Z. Tao and G. Wang, *Chem. Eng. J.*, 2022, **428**, 131075.
- 130 M. E. El-Naggar, S. I. Othman, A. A. Allam and O. M. Morsy, *Int. J. Biol. Macromol.*, 2020, **145**, 1115–1128.
- 131 C. Simón-Herrero, S. Caminero-Huertas, A. Romero, J. L. Valverde and L. Sánchez-Silva, *J. Mater. Sci.*, 2016, **51**, 8977–8985.
- 132 A. Mirtaghavi, J. Luo and R. Muthuraj, *J. Compos. Sci.*, 2020, **4**(4), 152.
- 133 J. Yan, T. Wu, Z. Ding and X. Li, *Carbohydr. Polym.*, 2016, **136**, 1288–1296.
- 134 G. M. Vladimirovich and V. P. Melnikov, *Graphene Oxide-Applications and Opportunities*, 2018, 39–55.
- 135 M. Kotal, J. Kim, J. Oh and I.-K. Oh, *Front. Mater.*, 2016, **3**, 29.
- 136 M. Berrio, A. Oñate, A. Salas, K. Fernández and M. Meléndrez, *Mater. Today Chem.*, 2021, **20**, 100422.
- 137 G. Nassar, E. Daou, R. Najjar, M. Bassil and R. Habchi, *Carbon Trends*, 2021, **4**, 100065.
- 138 R. Castaldo, R. Avolio, M. Cocca, M. E. Errico, M. Lavorgna, J. Šalplachta, C. Santillo and G. Gentile, *Chem. Eng. J.*, 2022, **430**, 133162.
- 139 Y. M. Shul'ga, E. Kabachkov, S. Baskakov and Y. V. Baskakova, *Russ. J. Phys. Chem.*, 2019, **93**, 296–300.
- 140 W. Chen, L. Yan and P. Bangal, *J. Phys. Chem. C*, 2010, **114**, 19885–19890.
- 141 S. P. Lee, G. A. Ali, H. Hegazy, H. N. Lim and K. F. Chong, *Energy Fuels*, 2021, **35**, 4559–4569.
- 142 K. Ghosh, C. Y. Yue, M. M. Sk, R. K. Jena and S. Bi, *Sustain. Energy Fuels*, 2018, **2**, 280–293.
- 143 M. Serrapede, M. Fontana, A. Gigot, M. Armandi, G. Biasotto, E. Tresso and P. Rivolo, *Materials*, 2020, **13**, 594.
- 144 T. Shen, Z. Zhao, Q. Zhong, Y. Qin, P. Zhang and Z.-X. Guo, *RSC Adv.*, 2019, **9**, 13042–13047.
- 145 Q. Zhang, W. Lu, M. Wu, G. Qi, Y. Yuan, J. Li, H. Su and H. Zhang, *J. Environ. Manage.*, 2022, **302**, 114044.
- 146 X. Wei, T. Huang, J.-H. Yang, N. Zhang, Y. Wang and Z.-W. Zhou, *J. Hazard. Mater.*, 2017, **335**, 28–38.
- 147 H. Ji, J. Li, J. Zhang and Y. Yan, *Composites, Part A*, 2019, **123**, 158–169.
- 148 Z. Zhao, X. Wang, J. Qiu, J. Lin, D. Xu, C. A. Zhang, M. Lv and X. Yang, *Rev. Adv. Mater. Sci.*, 2014, **36**, 137–151.
- 149 L. Jiang, Y. Wen, Z. Zhu, X. Liu and W. Shao, *Chemosphere*, 2021, **265**, 129169.
- 150 B. Anasori, M. R. Lukatskaya and Y. Gogotsi, *Nat. Rev. Mater.*, 2017, **2**, 1–17.
- 151 S. Shi, B. Qian, X. Wu, H. Sun, H. Wang, H. B. Zhang, Z. Z. Yu and T. P. Russell, *Angew. Chem., Int. Ed.*, 2019, **58**, 18171–18176.
- 152 X. Liu, Z. Lu, X. Huang, J. Bai, C. Li, C. Tu and X. Chen, *J. Power Sources*, 2021, **516**, 230682.
- 153 T. Chen, J. Wang, X. Wu, Z. Li and S. Yang, *Appl. Surf. Sci.*, 2021, **566**, 150719.
- 154 T. Shang, Z. Lin, C. Qi, X. Liu, P. Li, Y. Tao, Z. Wu, D. Li, P. Simon and Q. H. Yang, *Adv. Funct. Mater.*, 2019, **29**, 1903960.
- 155 Y.-Z. Zhang, J. K. El-Demellawi, Q. Jiang, G. Ge, H. Liang, K. Lee, X. Dong and H. N. Alshareef, *Chem. Soc. Rev.*, 2020, **49**, 7229–7251.
- 156 X. Zhou, J. Wen, X. Ma and H. Wu, *J. Colloid Interface Sci.*, 2022, **624**, 505–514.
- 157 Y. Deng, T. Shang, Z. Wu, Y. Tao, C. Luo, J. Liang, D. Han, R. Lyu, C. Qi and W. Lv, *Adv. Mater.*, 2019, **31**, 1902432.
- 158 T. Fukasawa, M. Ando, T. Ohji and S. Kanzaki, *J. Am. Ceram. Soc.*, 2001, **84**, 230–232.
- 159 G. Shao, D. A. H. Hanaor, X. Shen and A. Gurlo, *Adv. Mater.*, 2020, **32**, e1907176.
- 160 W. Liao, H.-B. Zhao, Z. Liu, S. Xu and Y.-Z. Wang, *Composites, Part B*, 2019, **173**, 107036.
- 161 B. Wicklein, A. Kocjan, G. Salazar-Alvarez, F. Carosio, G. Camino, M. Antonietti and L. Bergstrom, *Nat. Nanotechnol.*, 2015, **10**, 277–283.
- 162 M. Li, X. Dai, W. Gao and H. Bai, *Acc. Mater. Res.*, 2022, **3**, 1173–1185.
- 163 C. Wang, X. Chen, B. Wang, M. Huang, B. Wang, Y. Jiang and R. S. Ruoff, *ACS Nano*, 2018, **12**, 5816–5825.
- 164 P. Pieranski, *Phys. Rev. Lett.*, 1980, **45**, 569.
- 165 B. P. Binks, *Curr. Opin. Colloid Interface Sci.*, 2002, **7**, 21–41.
- 166 M. Kamkar, E. Erfanian, P. Bazazi, A. Ghaffarkhah, F. Sharif, G. Xie, A. Kannan, M. Arjmand, S. H. Hejazi and T. P. Russell, *Adv. Mater. Interfaces*, 2021, 2101659.
- 167 C. Huang, J. Forth, W. Wang, K. Hong, G. S. Smith, B. A. Helms and T. P. Russell, *Nat. Nanotechnol.*, 2017, **12**, 1060–1063.



- 168 J. Forth, X. Liu, J. Hasnain, A. Toor, K. Miszta, S. Shi, P. L. Geissler, T. Emrick, B. A. Helms and T. P. Russell, *Adv. Mater.*, 2018, **30**, 1707603.
- 169 A. Toor, S. Lamb, B. A. Helms and T. P. Russell, *ACS Nano*, 2018, **12**, 2365–2372.
- 170 M. Kamkar, A. Ghaffarkhah, R. Ajdary, Y. Lu, F. Ahmadijokani, S. E. Mhatre, E. Erfanian, U. Sundararaj, M. Arjmand and O. J. Rojas, *Small*, 2022, **18**, e2200220.
- 171 D. Smith, G. Scherer and J. Anderson, *J. Non-Cryst. Solids*, 1995, **188**, 191–206.
- 172 J. L. Gurav, I.-K. Jung, H.-H. Park, E. S. Kang and D. Y. Nadargi, *J. Nanomater.*, 2010, **2010**, 1–11.
- 173 Y. Cheng, S. Zhou, P. Hu, G. Zhao, Y. Li, X. Zhang and W. Han, *Sci. Rep.*, 2017, **7**, 1439.
- 174 H. Yang, Z. Li, B. Lu, J. Gao, X. Jin, G. Sun, G. Zhang, P. Zhang and L. Qu, *ACS Nano*, 2018, **12**, 11407–11416.
- 175 H. Hu, Z. Zhao, W. Wan, Y. Gogotsi and J. Qiu, *Adv. Mater.*, 2013, **25**, 2219–2223.
- 176 W. Zhang, Q. Q. Kong, Z. Tao, J. Wei, L. Xie, X. Cui and C. M. Chen, *Adv. Mater. Interfaces*, 2019, **6**, 1900147.
- 177 L. Li, M. Zhang, X. Zhang and Z. Zhang, *J. Power Sources*, 2017, **364**, 234–241.
- 178 Z. Yu, M. McInnis, J. Calderon, S. Seal, L. Zhai and J. Thomas, *Nano Energy*, 2015, **11**, 611–620.
- 179 Y. Jiang, S. Chowdhury and R. Balasubramanian, *J. Colloid Interface Sci.*, 2019, **534**, 574–585.
- 180 Y. Li, F. Meng, Y. Mei, H. Wang, Y. Guo, Y. Wang, F. Peng, F. Huang and Z. Zhou, *Chem. Eng. J.*, 2020, **391**, 123512.
- 181 Y. Yue, N. Liu, Y. Ma, S. Wang, W. Liu, C. Luo, H. Zhang, F. Cheng, J. Rao and X. Hu, *ACS Nano*, 2018, **12**, 4224–4232.
- 182 H. Bai, C. Li, X. Wang and G. Shi, *Chem. Commun.*, 2010, **46**, 2376–2378.
- 183 L. Liu, G. Kong, Y. Zhu and C. Che, *Colloids Interface Sci. Commun.*, 2021, **45**, 100518.
- 184 Z. Zhou, J. Liu, X. Zhang, D. Tian, Z. Zhan and C. Lu, *Adv. Mater. Interfaces*, 2019, **6**, 1802040.
- 185 X. Ming, A. Guo, Q. Zhang, Z. Guo, F. Yu, B. Hou, Y. Wang, K. P. Homewood and X. Wang, *Carbon*, 2020, **167**, 285–295.
- 186 X. P. Li, X. Li, H. Li, Y. Zhao, W. Li, S. Yan and Z. Z. Yu, *Adv. Sustainable Syst.*, 2021, **5**, 2100263.
- 187 M. Ding, S. Li, L. Guo, L. Jing, S. P. Gao, H. Yang, J. M. Little, T. U. Dissanayake, K. Li, J. Yang, Y. X. Guo, H. Y. Yang, T. J. Woehl and P. Y. Chen, *Adv. Energy Mater.*, 2021, **11**(35), 2101494.
- 188 Z. Wang, R. Wei, J. Gu, H. Liu, C. Liu, C. Luo, J. Kong, Q. Shao, N. Wang and Z. Guo, *Carbon*, 2018, **139**, 1126–1135.
- 189 Y. Dai, X. Wu, Z. Liu, H.-B. Zhang and Z.-Z. Yu, *Composites, Part B*, 2020, **200**, 108263.
- 190 A. M. Kaczmarek and R. Van Deun, *Chem. Soc. Rev.*, 2013, **42**, 8835–8848.
- 191 J. Hwang, A. Ejsmont, R. Freund, J. Goscianska, B. V. Schmidt and S. Wuttke, *Chem. Soc. Rev.*, 2020, **49**, 3348–3422.
- 192 X. Liu, T. Ma, N. Pinna and J. Zhang, *Adv. Funct. Mater.*, 2017, **27**, 1702168.
- 193 X. Zhao, W. Yao, W. Gao, H. Chen and C. Gao, *Adv. Mater.*, 2017, **29**, 1701482.
- 194 M. B. Coskun, L. Qiu, M. S. Arefin, A. Neild, M. Yuce, D. Li and T. Alan, *ACS Appl. Mater. Interfaces*, 2017, **9**, 11345–11349.
- 195 L. Sheng, Y. Liang, L. Jiang, Q. Wang, T. Wei, L. Qu and Z. Fan, *Adv. Funct. Mater.*, 2015, **25**, 6545–6551.
- 196 R. R. Nair, P. Blake, A. N. Grigorenko, K. S. Novoselov, T. J. Booth, T. Stauber, N. M. Peres and A. K. Geim, *Science*, 2008, **320**, 1308.
- 197 A. K. Geim and K. S. Novoselov, *Nat. Mater.*, 2007, **6**, 183–191.
- 198 A. A. Balandin, S. Ghosh, W. Bao, I. Calizo, D. Teweldebrhan, F. Miao and C. N. Lau, *Nano Lett.*, 2008, **8**, 902–907.
- 199 L. Xu, G. Xiao, C. Chen, R. Li, Y. Mai, G. Sun and D. Yan, *J. Mater. Chem. A*, 2015, **3**, 7498–7504.
- 200 Z. Sui, X. Zhang, Y. Lei and Y. Luo, *Carbon*, 2011, **49**, 4314–4321.
- 201 H. Chang, J. Qin, P. Xiao, Y. Yang, T. Zhang, Y. Ma, Y. Huang and Y. Chen, *Adv. Mater.*, 2016, **28**, 3504–3509.
- 202 H. Hu, Z. Zhao, W. Wan, Y. Gogotsi and J. Qiu, *Adv. Mater.*, 2013, **25**, 2219–2223.
- 203 L. Liu, M. Qing, Y. Wang and S. Chen, *J. Mater. Sci. Technol.*, 2015, **31**, 599–606.
- 204 F. Kim, L. J. Cote and J. Huang, *Adv. Mater.*, 2010, **22**, 1954–1958.
- 205 B. Wicklein, A. Kocjan, G. Salazar-Alvarez, F. Carosio, G. Camino, M. Antonietti and L. Bergström, *Nat. Nanotechnol.*, 2015, **10**, 277–283.
- 206 Z.-Z. Pan, H. Nishihara, S. Iwamura, T. Sekiguchi, A. Sato, A. Isogai, F. Kang, T. Kyotani and Q.-H. Yang, *ACS Nano*, 2016, **10**, 10689–10697.
- 207 G. Zu, K. Kanamori, K. Nakanishi, X. Lu, K. Yu, J. Huang and H. Sugimura, *ACS Appl. Mater. Interfaces*, 2019, **11**, 43533–43542.
- 208 K. Chen, X. Tang, B. Jia, C. Chao, Y. Wei, J. Hou, L. Dong, X. Deng, T.-H. Xiao, K. Goda and L. Guo, *Nat. Mater.*, 2022, **21**, 1121–1129.
- 209 Z. Ouyang, C. Wang, D. Xu, H.-Y. Yu, Y. Zhou, M. Mu, D. Ge, Z. Miao and K. C. Tam, *Macromol. Mater. Eng.*, 2022, **307**, 2100834.
- 210 M. Yang, N. Zhao, Y. Cui, W. Gao, Q. Zhao, C. Gao, H. Bai and T. Xie, *ACS Nano*, 2017, **11**, 6817–6824.
- 211 J. E. Kim, T. H. Han, S. H. Lee, J. Y. Kim, C. W. Ahn, J. M. Yun and S. O. Kim, *Angew. Chem.*, 2011, **123**, 3099–3103.
- 212 Z. Xu and C. Gao, *ACS Nano*, 2011, **5**, 2908–2915.
- 213 Z. Xu and C. Gao, *Nat. Commun.*, 2011, **2**, 1–9.
- 214 Z. Liu, Z. Li, Z. Xu, Z. Xia, X. Hu, L. Kou, L. Peng, Y. Wei and C. Gao, *Chem. Mater.*, 2014, **26**, 6786–6795.
- 215 Z. Xu and C. Gao, *Acc. Chem. Res.*, 2014, **47**, 1267–1276.
- 216 Y. Li, W. Wei, Y. Wang, N. Kadhim, Y. Mei and Z. Zhou, *J. Mater. Chem. C*, 2019, **7**, 11783–11789.
- 217 N. Graeber, *Imperial College London*, 2013.
- 218 M. Naguib, M. Kurtoglu, V. Presser, J. Lu, J. Niu, M. Heon, L. Hultman, Y. Gogotsi and M. W. Barsoum, *Adv. Mater.*, 2011, **23**, 4248–4253.
- 219 B. Anasori and Ū. G. Gogotsi, *2D metal carbides and nitrides (MXenes)*, Springer, 2019.
- 220 N. C. Frey, J. Wang, G. I. N. Vega Bellido, B. Anasori, Y. Gogotsi and V. B. Shenoy, *ACS Nano*, 2019, **13**, 3031–3041.
- 221 M. Naguib, O. Mashtalir, J. Carle, V. Presser, J. Lu, L. Hultman, Y. Gogotsi and M. W. Barsoum, *ACS Nano*, 2012, **6**, 1322–1331.



