

voltage, ease of manufacturing, high transconductance, and biocompatibility, OECTs are ideal for chemical and biological sensing,^{20–22} large-area printed circuitry,²³ and neuromorphic computing.^{24–40}

While the progress in OECT-based circuitry has primarily revolved around the exploration of the hole-transporting (p-type) polymer PEDOT:PSS,^{41–45} recent advances in the design and synthesis of p-type and n-type (electron-transporting) OMIECs have led to the development of power-efficient complementary OECT technologies.^{46–48} These advancements have not only opened new possibilities for achieving improved performance and energy efficiency in OECT-based amplifiers^{49,50} and digital logics⁴⁶ but also facilitated the development of the first leaky-integrate-and-fire (LIF) type organic electrochemical neuron (OECN) with ion-modulated spiking.²⁴ The breakthrough holds great promise for bioelectronic applications, enabling the development of event-based sensors capable of local sensing, signal processing, and stimulation of the nervous system. This requires the development of OECNs capable of operating stably with spike dynamics and voltage output on par with biology. However, the initial implementation of LIF-OECNs suffered from a low spiking frequency (20–200 mHz) and reduced voltage output during continuous operation for over 1 h. Although reducing the OECT channel dimensions could increase the spiking frequency, the instability of the output current in the p-type OECT remains a significant hurdle, leading to output voltage drop and poor operational stability. Therefore, developing stable p-type OMIECs is crucial for achieving high-performance OECNs and enabling their widespread implementation in bioelectronics.

Several p-type OMIECs have been reported for complementary OECT technologies, including the conjugated polyelectrolyte poly(3-carboxypentylthiophene) (P3CPT), as well as conjugated polymers bearing glycolated side chains such as p(g₄2T-T), p(gTDPPT), and gDPP-g2T.^{46,48,51–53} These p-type OMIECs exhibit excellent charge carrier mobility and large volumetric capacitance. However, several of them suffer from degradation during continuous operation in ambient. Strategies to improve the stability of p-type OMIECs include designing encapsulation layers⁵⁴ or tuning the polymer's energetics^{55,56} to suppress electrochemical side reactions during OECT operation, incorporating high-boiling-point solvents and Lewis acids to alter the polymer chain arrangements and prevent oxidative degradation,⁵⁷ and optimizing the polymer side chain distribution to regulate swelling and enhance stability.^{58,59} However, p-type OMIECs with improved stability often experience lower mobilities and volumetric capacitances, resulting in overall low complementary device performance.

Ladder-type polymers possess a rigid backbone structure consisting of double-strand chains linked by condensed π -conjugated units. This unique structure allows them to sustain high levels of chemical/electrochemical doping without experiencing conformational disorder.^{26,60,61} As a result, ladder-type polymers exhibit exceptional operational stability, high charge carrier mobility, and large volumetric capacitance.⁵¹ One prominent example of a ladder-type polymer is the n-type poly(benzimidazobenzophenanthroline) (BBL), which

demonstrates outstanding operational stability in OECTs.⁴⁸ Recently, Li *et al.*⁶² reported the ladder-type polymer poly[pyrrolo[3,2-*b*:4,5-*b'*]bis-[1,4]benzothiazine] (PBBT), which can function as a p-type OMIEC. While PBBT shows decent stability when used as the channel material of OECTs, it suffers from low mobility and low volumetric capacitance.⁶³

Here, we present a practical approach to enhancing the mobility, volumetric capacitance, and stability of PBBT through backbone engineering. Our strategy involves methylating the PBBT polymer backbone to obtain the polymer poly[6-methylpyrrolo[3,2-*b*:4,5-*b'*]bis-[1,4]benzothiazine] (PBBT-Me, Fig. 1(a)). Notably, this subtle backbone modification leads to significant improvements in the material properties, including a remarkable 25-fold increase in hole mobility and an impressive 36-fold increase in μC^* of PBBT-Me as compared to the non-methylated polymer PBBT-H, while maintaining similar stability. Using this newly developed polymer in combination with BBL, we successfully demonstrate complementary inverters with a record-high DC gain of 194 V V⁻¹ and excellent stability. These state-of-the-art complementary inverters are then used to develop LIF-OECNs with firing frequencies of about 2 Hz and capable of continuous operation for up to 6.5 h. This achievement represents a substantial improvement compared to previous results and holds great potential for the development of stable bioelectronic circuits capable of in-sensor computing.

Results and discussion

PBBT-H and PBBT-Me were synthesized through a polycondensation reaction of 2,3-dibromomaleimide (Br₂MIH) or 2,3-dibromomethylmaleimide (Br₂MIMe) and 2,5-diaminobenzene-1,4-dithiol dihydrochloride (DABDT) in a 1:1 polyphosphoric acid (PPA):phenylphosphonic acid⁶⁴ (PhP(O)(OH)₂) mixture at 180 °C (Fig. 1(a)). Fourier transform infrared spectroscopy and X-ray photoelectron spectroscopy confirmed successful methylation of the PBBT polymer backbone (Fig. S1 and S2, ESI[†]). Both ladder-type polymers have good solubility in methanesulfonic acid (MSA) at concentrations over 10 mg mL⁻¹ and can be deposited in thin films by spin-coating their MSA solutions onto substrates at room temperature. The intrinsic viscosities of PBBT-H and PBBT-Me were measured to be 0.94 dL g⁻¹ and 0.99 dL g⁻¹ (in MSA, 25 °C), respectively, which indicates comparable molecular weights. Additionally, both polymers are thermally stable with decomposition temperatures over 540 °C, and no phase transitions were observed before decomposition (Fig. S3, ESI[†]).

Cyclic voltammetry measurements show that PBBT-H and PBBT-Me have highest occupied molecular orbital (HOMO) energy levels of -5.06 eV and -4.87 eV, respectively. These measurements suggest that the electron-donating effect of the methyl group makes the HOMO level of PBBT-Me shallower by 0.2 eV. The UV-Vis-NIR absorption spectra of the two polymers in diluted MSA solutions show two absorption bands located at 300–600 nm and 800–1100 nm, respectively (Fig. 1(c)). The introduction of the methyl group in PBBT-Me compared to PBBT-H results in a redshift of the π - π transition in the range





Fig. 1 Synthesis and physicochemical properties of PBTT-H and PBTT-Me. (a) Synthetic route of PBTT-H and PBTT-Me. (b) CV of PBTT-H and PBTT-Me in 0.1 M $n\text{-Bu}_4\text{NPF}_6$ acetonitrile solution. (c) and (d) UV-vis-NIR absorption spectra of PBTT-H and PBTT-Me in diluted MSA solutions (c) and thin films (d).

800–1100 nm. This redshift indicates that the methyl group further enhances the electron-rich nature of the pyrrole unit, leading to a narrowing of the bandgap (E_g) in the protonated state in solution. The absorption spectra of the two polymers in the thin film state are also similar, with a slight redshifted absorption onset wavelength (λ_{onset}) for PBTT-Me (Fig. 1(d)). Note that the maximum absorption peaks in solutions are redshifted compared to those in thin films likely due to protonation of the polymer backbone in solution. With the λ_{onset} of PBTT-H being 829 nm and λ_{onset} of PBTT-Me being 868 nm, the optical E_g is calculated to be 1.50 eV for PBTT-H and 1.43 eV for PBTT-Me.

Next, we investigated PBTT-H and PBTT-Me thin film microstructure using grazing-incidence wide-angle X-ray scattering (GIWAXS) and atomic force microscopy (AFM). GIWAXS analysis (Fig. 2(a)–(c)) reveals that PBTT-H chains are arranged preferentially face-on on the substrate, while PBTT-Me chains are mostly oriented edge-on. Both PBTT-H and PBTT-Me display strong π - π stacking (010) peaks located at 1.82 \AA^{-1} , indicative of a similar π - π stacking distance $d_{\pi-\pi} = 3.45 \text{ \AA}$ (Fig. 2(c) and Fig. S4, ESI[†]). However, PBTT-H exhibits a lamellar packing distance $d_{\text{lamellar}} = 8.73 \text{ \AA}$ [(100) peak at $q_{xy} = 0.72 \text{ \AA}^{-1}$], which is shorter than PBTT-Me's $d_{\text{lamellar}} = 9.82 \text{ \AA}$ [(100) peak at $q_z = 0.64 \text{ \AA}^{-1}$]. The observed difference in packing distance is consistent with the presence of the methyl group on

the PBTT-Me backbone. Furthermore, PBTT-Me shows significantly enhanced π - π stacking crystallinity with smaller FWHM (0.1677 for PBTT-Me vs. 0.3256 for PBTT-H), longer coherence length (33.3 \AA for PBTT-Me vs. 17.2 \AA for PBTT-H), and smaller paracrystalline disorder (0.121 for PBTT-Me vs. 0.169 for PBTT-H) as shown in Fig. S4 and S5 of the ESI[†]. These results suggest that PBTT-Me may be more efficient in transporting charge carriers in the in-plane direction than PBTT-H. The AFM analysis shows that both PBTT-H and PBTT-Me thin films have a flat polycrystalline morphology (Fig. 2(d) and (e)). The surface roughness of PBTT-H was measured to be 7.89 nm, whereas PBTT-Me displayed a slightly smaller roughness of 6.15 nm. A summary of the solid-state microstructure characteristics can be found in Table 1.

Spectroelectrochemistry was performed to investigate the electronic structure of electrochemically doped PBTT-H and PBTT-Me thin films. The polymer thin films were coated on ITO substrates and subjected to a voltage bias applied to the Ag/AgCl electrode through a 0.1 M NaCl aqueous electrolyte (Fig. 3(a), (b) and Fig. S6 in the ESI[†]). Upon applying an oxidation voltage bias within the 0–1 V range, we observed that both PBTT-H and PBTT-Me undergo electrochemical doping with clear bleaching of the ground state (370–800 nm) and strong polaron absorption (> 800 nm). The PBTT-H's polaronic species arise at an oxidation voltage of around 0.4 V, whereas





Fig. 2 Thin-film microstructures. (a) and (b) 2D GIWAXS patterns of PBBT-H (a) and PBBT-Me (b). (c) In-plane and out-of-plane GIWAXS line cuts of PBBT-H and PBBT-Me thin films. (d) and (e) AFM height images of PBBT-H (d) and PBBT-Me (e). The root mean square (RMS) surface roughness is also reported. (f) and (g) Schematic of the PBBT-H and PBBT-Me chains packing.

Table 1 Summary of the energy level and solid-state microstructure of PBBT-H and PBBT-Me

Polymer	E_g (eV)	HOMO (eV)	LUMO (eV)	Orientation	d_{lamellar} (Å)	$d_{\pi-\pi}$ (Å)	$L_{c, \pi-\pi}$ (Å)
PBBT-H	1.50	-5.06	-3.56	Face-on	8.73	3.45	17.2
PBBT-Me	1.43	-4.87	-3.44	Edge-on	9.82	3.45	33.3

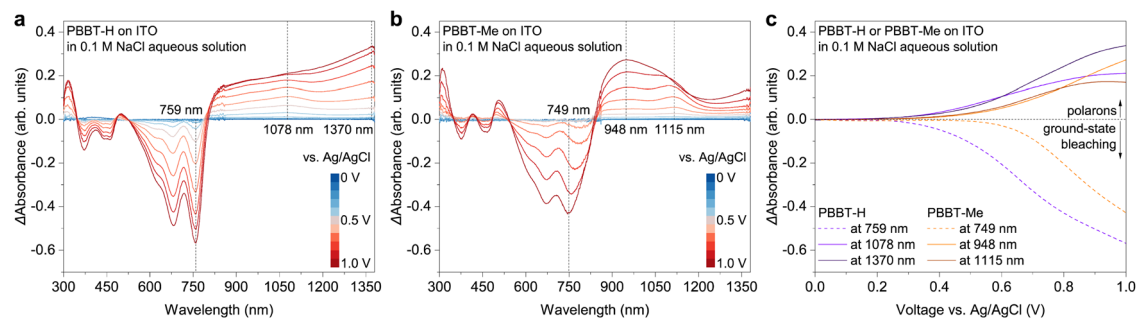


Fig. 3 Differential spectroelectrochemistry. (a) and (b) Differential absorption spectra of PBBT-H (a) and PBBT-Me (b). (c) Differential absorption spectra of PBBT-H (c) and PBBT-Me (d) at select wavelengths. In all these spectroelectrochemistry measurements, 0.1 M NaCl aqueous solution was used as the electrolyte, Ag/AgCl electrode was grounded, and the voltage was applied to the polymer films scanning between 0 V and 1.0 V versus Ag/AgCl electrode.

those of PBBT-Me form at around 0.5 V (Fig. 3(c)). We attributed this difference to the introduction of the methyl group in PBBT-Me, which resulted in a slight increase in hydrophobicity (Fig. S14, ESI[†]), ultimately leading to a minor increase in the oxidation threshold.

Next, we conducted a comprehensive characterization of the performance of PBBT-H and PBBT-Me in OECTs. OECTs were

prepared by following the procedure reported in the Experimental Section, which involves using glass wafers with patterned metal and parylene layers. The channel materials were deposited onto the OECT substrates from their MSA solutions *via* spin-coating and then patterned using a sacrificial layer of parylene to produce the OECT channel ($W/L = 400 \mu\text{m}/6 \mu\text{m}$). The thickness of the polymer thin films (50 nm) was adjusted





Fig. 4 OECT performance. (a), (b) Output characteristics of OECTs based on PBTT-H (a) and PBTT-Me (b). (c), (d) Transfer characteristics of OECTs based on PBTT-H (c) and PBTT-Me (d). (e), (f) Geometry-normalized transconductance ($g_{m, \text{norm}}$) of PBTT-H (e) and PBTT-Me (f). Inset: Schematic of the OECTs. (g) and (h) Stability of OECTs based on PBTT-H (g) and PBTT-Me (h).

by controlling the concentration of the MSA solution. The OECT was then completed using 0.1 M NaCl aqueous solution as the electrolyte and an Ag/AgCl pellet as the gate electrode (Fig. S7, ESI†). Both PBTT-H and PBTT-Me exhibit typical p-type accumulation-mode characteristics, as evidenced by their output and transfer curves (Fig. 4(a)–(d)). The ON/OFF ratio of OECTs using PBTT-H and PBTT-Me as the channel materials are $4.5(\pm 0.5) \times 10^3$ and $2.5(\pm 0.3) \times 10^6$, respectively (Fig. 4(c) and (d)). The on-state current of PBTT-Me-based OECTs at $V_D = V_G = -0.7$ V is 511 ± 26 μA , which is approximately $10\times$ higher than that of PBTT-H (50 ± 2 μA). The threshold voltage of PBTT-Me OECTs (0.52 ± 0.01 V) is slightly larger than that of PBTT-H (0.36 ± 0.01 V), and consistent with the spectroelectrochemistry experiments. The μC^* values of PBTT-H and PBTT-Me were calculated to be 2.5 ± 0.1 $\text{F cm}^{-1} \text{V}^{-1} \text{s}^{-1}$ and 92.3 ± 5.0 $\text{F cm}^{-1} \text{V}^{-1} \text{s}^{-1}$, respectively (Fig. S8, ESI†). Electrochemical impedance spectroscopy (EIS) was used to evaluate the volumetric capacitance C^* of the two polymers, resulting in values of 179 ± 5 F cm^{-3} for PBTT-H and 259 ± 6 F cm^{-3} for PBTT-Me (Fig. S9–S11, ESI†). Thus, the μ_{OECT} of PBTT-H and PBTT-Me was calculated to be $(1.41 \pm 0.04) \times 10^{-2}$ $\text{cm}^2 \text{V}^{-1} \text{s}^{-1}$ for PBTT-H and 0.356 ± 0.028 $\text{cm}^2 \text{V}^{-1} \text{s}^{-1}$ for PBTT-Me. The higher mobility of PBTT-Me is consistent with the increased on-state current of PBTT-Me OECTs compared to PBTT-H OECTs and can be

explained by the increased crystallinity, longer coherence length, and preferential edge-on orientation of PBTT-Me compared to PBTT-H, as revealed by the GIWAXS data (*vide supra*). This edge-on arrangement facilitates interchain hole transport, leading to more efficient charge transport in PBTT-Me. In addition, the max $g_{m, \text{norm}}$ of PBTT-Me is also increased by one order of magnitude compared to PBTT-H, from 1.11 ± 0.02 S cm^{-1} to 40.6 ± 1.5 S cm^{-1} . Both PBTT-H and PBTT-Me OECTs exhibit remarkably high stability, with over 90% of the initial drain current retained after more than 4 hours of continuous operation ($V_D = V_G = -0.6$ V). This stability is among the highest reported for p-type OECTs (Fig. S12 and Table S1, ESI†).^{55–59} The PBTT-H OECTs have a transient response $\tau_{\text{ON}} = 0.74 \pm 0.02$ ms, while that of PBTT-Me OECT is slightly slower at 3.19 ± 0.05 ms (Fig. S13, ESI†), likely due to the increased hydrophobicity of PBTT-Me layer (Fig. S14, ESI†). Table 2 summarizes the OECT characteristics of the two polymers.

To investigate their usage in circuits, we developed complementary electrochemical inverters utilizing PBTT-H or PBTT-Me as the hole-transporting materials and BBL as the electron-transporting material due to its low $V_{\text{th}} = 0.15$ V, high on/off ratio of 10^5 , and high $g_{m, \text{norm}} = 11$ S cm^{-1} (Fig. S15, ESI†). The OECT-based inverter schematic is presented in Fig. 5(a) and (b). The pull-up PBTT-H or PBTT-Me-based transistor in the

Table 2 Summary of OECT performance of PBTT-H and PBTT-Me

Polymer	$g_{m, \text{norm}}$ (S cm^{-1})	V_{th} (V)	$I_{\text{ON}}/I_{\text{OFF}}$	μC^* ($\text{F cm}^{-1} \text{V}^{-1} \text{s}^{-1}$)	C^* (F cm^{-3})	μ ($\text{cm}^2 \text{V}^{-1} \text{s}^{-1}$)	$\tau_{\text{ON}}, \tau_{\text{OFF}}$ (ms)
PBTT-H	1.11 ± 0.02	-0.36 ± 0.01	4×10^3	2.52 ± 0.07	179 ± 5	$(1.41 \pm 0.04) \times 10^{-2}$	$0.738 \pm 0.018, 0.138 \pm 0.011$
PBTT-Me	40.6 ± 1.5	-0.52 ± 0.02	2×10^6	92.3 ± 5.0	259 ± 6	0.356 ± 0.028	$3.19 \pm 0.02, 0.159 \pm 0.014$





Fig. 5 OECT-based inverters. (a) and (b) Typical voltage transfer characteristics (VTC) of the inverters at various supply voltages (from 0.2 to 0.7 V). (c) and (d) Voltage gains of the inverters at various supply voltages. (e) and (f) Input and output of the inverters showing "0" and "1" states. All the above inverters consisted of an n-type (BBL) and a p-type OECT (PBBT-H or PBBT-Me) OECT.

OECT-based inverter switches on and off in response to a gradual change in gate voltage (V_{in}) between 0 V and $V_{in} = V_{DD}$, while the pull-down BBL-based transistor works in the opposite manner. As a result, the inverter's output voltage (V_{out}) switches between approximately V_{DD} and 0 V in response to V_{in} , as shown in Fig. 5(a) and (b). PBBT-H-based inverters operate at

V_{DD} as low as 0.2 V with voltage gains $> 8 \text{ V V}^{-1}$ (Fig. 5(c)), while PBBT-Me-based inverters exhibit voltage gains $> 20 \text{ V V}^{-1}$ at $V_{DD} = 0.3 \text{ V}$ (Fig. 5(d)), note that the threshold voltage of PBBT-Me based OECTs is 0.15 V higher than that of PBBT-H OECTs). At $V_{DD} = 0.7 \text{ V}$, PBBT-H-based inverters exhibit voltage gains of about 60 V V^{-1} , while PBBT-Me-based inverters reach record



Fig. 6 Organic electrochemical neurons based on PBBT-Me and BBL. (a) Schematic of the leaky-integrate-and-fire (LIF) type spiking neuron, comprising both p-type and n-type accumulation-mode OECTs. (b) Typical spiking behaviors of a LIF-neuron based on PBBT-Me and BBL, gated using Ag/AgCl and working at $I_{in} = 2 \mu\text{A}$ in 0.1 M NaCl aqueous solution. (c) Spiking frequency and $V_{fire,max}$ of the LIF-neuron at different I_{in} . (d) Spiking patterns at $I_{in} = 2 \mu\text{A}$ for 0 h, 3 h, and 6.5 h. (e) Spiking frequencies of the LIF-neuron change over time at $I_{in} = 0.25 \mu\text{A}$, $1 \mu\text{A}$, $6 \mu\text{A}$ during 6.5 h of continuous operation. (f) Evolution of the $V_{fire,max}$ over time at $I_{in} = 0.25 \mu\text{A}$, $1 \mu\text{A}$, $6 \mu\text{A}$ during 6.5 h of continuous operation.



high voltage gains of 194 V V^{-1} , which is among the highest reported for complementary OECT inverters (Fig. S16 and Table S2, ESI†). Mixing PBBT-Me and BBL yields ambipolar mixtures with balanced hole and electron transport, resulting in complementary inverters with voltage gains larger than those recently reported for PBBT-L:BBL blends⁶³ (Fig. S17, ESI†). This is consistent with the fact that PBBT-Me has significantly higher mobility and μC^* than PBBT-H. Both PBBT-H and PBBT-Me-based inverters show exceptionally low static power consumption, ranging from 0.5 nW ($V_{\text{DD}} = 0.2 \text{ V}$) to 40 nW ($V_{\text{DD}} = 0.7 \text{ V}$), as well as peak power consumption during switching below $10 \text{ }\mu\text{W}$ (Fig. S18, ESI†). Additionally, these inverters demonstrate swift transient switching with small τ_{ON} and τ_{OFF} in the range of $1.5\text{--}4 \text{ ms}$ (Fig. 5(e), (f) and Fig. S19, ESI†) and remarkable cycling stability (Fig. S20, ESI†). Considered altogether, these inverter characteristics are among the best reported for sub-1 V complementary inverters.^{46,49,52,63,65–69}

Finally, we used the complementary electrochemical inverters described above to develop LIF type OECNs based on a modified version of the Axon-Hillock circuit (Fig. 6(a)).²⁴ The OECNs comprising the p-type PBBT-Me and n-type BBL OECTs can fire at a frequency nearing 2 Hz and with voltage spike amplitude ($V_{\text{fire,max}}$) of around 0.4 V at input currents $I_{\text{in}} > 2 \text{ }\mu\text{A}$ (Fig. 6(b)–(d) and Fig. S21, S22 in the ESI†). OECNs made of the ambipolar PBBT-Me:BBL mixture show comparable spiking characteristics (Fig. S23 and S24, ESI†). This biologically plausible spiking frequency could mimic most neural firing rates and can be used to stimulate biological nerves.³³ These OECNs can also be made solid state by using printable hydrogels⁴⁶ based on polycationic polyquaturnium-10 (PQ-10) for PBBT-Me OECTs and polyanionic poly(sodium-4-styrene sulfonate) (PSSNa) for BBL OECTs (Fig. S25 and S26 in the ESI†). Remarkably, these OECNs retain close to 90% of the initial spiking frequencies and voltage amplitudes for over 6.5 h of continuous spiking, outperforming similar LIF-OECNs comprising the p-type P(g₄2T-T) (Fig. S27 and S28, ESI†). This excellent operational stability is paramount for the development of stable event-based sensors.

Conclusion

In conclusion, we demonstrated that simple methylation of PBBT-based ladder-type polymers yields a p-type OMIEC with notable OECT performance (*i.e.*, $g_{\text{m,norm}} = 40.6 \pm 1.5 \text{ S cm}^{-1}$, $\mu C^* = 92.3 \pm 5.0 \text{ F cm}^{-1} \text{ V}^{-1} \text{ s}^{-1}$, and $\tau_{\text{ON}} = 3.19 \pm 0.02 \text{ ms}$). We attributed these remarkable characteristics to an enhanced intermolecular charge transport, which results from a rearrangement of the polymer chains induced by the introduction of the methyl group in the PBBT polymer backbone. In addition, the rigid ladder-type polymer backbone endows PBBT-Me with outstanding electrochemical stability, making it suitable for long-term operation. Complementary inverters based on PBBT-Me and BBL exhibit record-high voltage gains $> 190 \text{ V V}^{-1}$, low static power consumption $< 40 \text{ nW}$, and excellent operational stability. This allowed us to build LIF-type OECNs with a stable

operation for $> 6.5 \text{ h}$ without significant degradation in terms of firing frequency ($1\text{--}2 \text{ Hz}$) and voltage amplitude ($0.4\text{--}0.5 \text{ V}$). These results open the path for developing high-performance complementary OECT-based amplifiers and artificial neurons for brain-inspired electronics.

Experiment section

Synthesis

2,5-Diamino-1,4-benzenedithiol dihydrochloride (DABDT) was purchased from Tokyo Chemical Industry. 2,3-Dibromomaleimide (Br₂MIH), polyphosphoric acid (PPA), phenylphosphonic acid (PhP(O)(OH)₂), *N*-methylpyrrole, tetrahydrofuran (THF), *N*-bromosuccinimide (NBS) and methanesulfonic acid (MSA), *n*-hexane, nitric acid, ethyl acetate were purchased from Sigma-Aldrich.

N-Methyl-3,4-dibromomaleimide (Br₂MIME), the polymerization precursor of PBBT-Me, was synthesized following a reported procedure.⁷⁰ *N*-Methylpyrrole (6.00 g , 73.97 mmol) was placed in a three-necked round-bottom flask, then dry THF (200 mL) was added and the system was kept under nitrogen atmosphere. After *N*-methylpyrrole was completely dissolved, the solution was cooled to $-78 \text{ }^\circ\text{C}$. NBS powder (74.17 g , 416.73 mmol) was added in 10 portions during 20 minutes to keep the mixture at a low temperature. The mixture was stirred for 30 minutes at this temperature, then restored to room temperature and stirred for 12 hours. The solvent was removed by distillation under reduced pressure, and 20 mL of dichloromethane was added to the residual solid. The dichloromethane solution was isolated by filtration, concentrated to 10 mL , transferred to a 100 mL single-necked bottle and placed in ice bath. Concentrated nitric acid was added dropwise to make sure the temperature of the mixture wouldn't increase. The reaction mixture was kept at $0 \text{ }^\circ\text{C}$ for 3 hours. The obtained solution was subsequently quenched with ice and water mixture and ethyl acetate ($3 \times 50 \text{ mL}$) was used to extract the soluble fraction. The organic layer was collected, successively washed with water, sodium bicarbonate, and brine, dried over anhydrous Na₂SO₄ and concentrated. The crude product was recrystallized from ethanol, and the final product Br₂MIME was obtained as colorless needles with 84% (16.77 g) yield. NMR: ¹H (300 MHz , DMSO-d₆): δ [ppm] 2.95 (s, 3H).

PBBT-Me was synthesized based on a procedure reported before.⁶⁴ PPA (26 g) and PhP(O)(OH)₂ (26 g) were added to a 250 mL three-necked flask fitted with an overhead stirrer and nitrogen inlet/outlet. The mixture of PPA and PhP(O)(OH)₂ was deoxygenated by heating at $110 \text{ }^\circ\text{C}$ for 2 hours with nitrogen bubbling through. The solution was cooled to room temperature and 2.00 g (8.16 mmol) of DABDT was added. The mixture was heated at $80 \text{ }^\circ\text{C}$ for 12 hours to remove HCl, then Br₂MIME (2.19 g , 8.16 mmol) was added. This solution was heated at $80 \text{ }^\circ\text{C}$ for another 12 hours, then heated at $150 \text{ }^\circ\text{C}$ for 24 hours. Next, the temperature was gradually increased to $180 \text{ }^\circ\text{C}$ and kept for 48 hours to complete the polymerization. The obtained



black solution was cooled to room temperature and poured into 1 L of ethanol with the aid of a stirrer for better mixing. The obtained polymer precipitate was collected by filtration and washed with ethanol. It was then re-dissolved into methanesulfonic acid and re-precipitated in 1 L of ethanol. Again, the solid was collected by filtration, washed thoroughly with water and ethanol, and dried in vacuum to yield brown solid product PBBT-Me (1.97 g, 99.3% yield, $\eta = 0.989 \text{ dL g}^{-1}$ in MSA at 30 °C, $M_v = 8.82 \text{ kDa}$). In estimation of M_v , the viscosity was measured with an Ubbelohde viscometer and calculated with^{48,71} $K = 5.11 \times 10^{-6} \text{ g dL}^{-1}$ and $\alpha = 1.34$. Elemental anal. calcd for $\text{C}_{11}\text{H}_5\text{N}_3\text{S}_2$: C, 54.3; H, 2.1; N, 17.3; S, 26.4; found: C, 52.5; H, 2.6; N, 16.2; S, 28.5.

PBBT-H was synthesized following a reported procedure.⁶⁴ The same setup was used as in PBBT-Me synthesis, and the synthesis procedure was similar, except that the reactant DBMI-Me was replaced with 2,3-dibromomaleimide. In brief, PPA (21 g) and PhP(O)(OH)_2 (21 g) were added to a 250 mL three-necked flask fitted with an overhead stirrer and nitrogen inlet/outlet. The mixture of PPA and PhP(O)(OH)_2 was heated at 110 °C for 2 hours with nitrogen bubbling through. Then, the solution was cooled to room temperature, and 1.64 g (6.68 mmol) of DABDT was added. The reaction mixture was heated at 80 °C for 12 hours to remove HCl, and then Br_2MIH (1.70 g, 6.68 mmol) was added. This mixture was kept at 80 °C for another 12 hours. Next, the solution was heated at 150 °C for 24 hours and then the temperature was gradually increased to 180 °C. The reaction mixture was kept at 180 °C for 48 hours to obtain PBBT-H polymer. The post-processing was the same as that of PBBT-Me. The final product PBBT-H was yield as brown solid product PBBT-H (1.27 g, 85% yield, $\eta = 0.938 \text{ dL g}^{-1}$ in MSA at 30 °C, $M_v = 8.48 \text{ kDa}$). In estimation of M_v , the viscosity was measured with an Ubbelohde viscometer and calculated with^{71,72} $K = 5.11 \times 10^{-6} \text{ g dL}^{-1}$ and $\alpha = 1.34$. Elemental anal. calcd for $\text{C}_{10}\text{H}_3\text{N}_3\text{S}_2$: C, 52.4; H, 1.3; N, 18.3; S, 28.0; found: C, 48.3; H, 2.3; N, 15.0; S, 25.6.

Thin-film casting

PBBT-H and PBBT-Me were dissolved in MSA at 60 °C for 2 hours and subsequently cooled to room temperature. The solutions were then spin-cast (1000 rpm, 60 s, acceleration 1000 rpm s^{-1}) onto glass, ITO-glass or Si/SiO₂ substrates to form thin films. The substrates covered with polymer films were immersed into deionized water to remove residual MSA and then blown dry with nitrogen. The concentration of the polymer solution was adjusted between 2–11 mg mL^{-1} to obtain thin films with thickness of 20–100 nm.

Absorption spectra

Absorption spectra were performed with 7 $\mu\text{g mL}^{-1}$ polymer-MSA solutions and 70 nm-thick polymer thin films on glass slides. Spectroelectrochemistry measurement was performed with indium tin oxide (ITO) glass substrates spin-cast on 70 nm-thick polymer thin films. The polymer films were grounded, and the substrates were immersed in 0.1 M NaCl

solution, serving as the electrolyte. An Ag/AgCl pellet was used as the gate electrode applied with specific voltages through Keithley 4200A-SCS. Each voltage step was kept for 200 s before absorption spectra measuring, which was carried out with PerkinElmer Lambda 900 spectrometer at 25 °C.

Electrochemistry

Electrochemical measurements were carried out with Potentiostat Biologic SP-200. In CV measurement, deoxygenized 0.1 M *n*-Bu₄NPF₆ anhydrous acetonitrile solution served as the electrolyte, saturated Ag/AgCl electrode worked as the reference electrode (RE), and a 10 mm × 10 mm platinum mesh was used as the counter electrode (CE). PBBT-H and PBBT-Me thin-films were spin-cast from 5 mg mL^{-1} MSA solutions onto chromium (5 nm)/gold (50 nm) deposited glass slides (5 mm × 5 mm) to make working electrode (WE). The scan rate used for CV measurement was 50 mV s^{-1} . In electrochemical impedance spectroscopy (EIS) measurement, the electrolyte was 0.1 M NaCl aqueous solution, the RE was a saturated Ag/AgCl electrode, and the CE was a 10 mm × 10 mm platinum mesh. Cr/Au electrodes (on glass slides) were deposited with different amount of polymers through spin-coating to form films with various volumes. The obtained PBBT-H or PBBT-Me film with a volume of 7.5×10^{-7} – $5.1 \times 10^{-6} \text{ cm}^3$ serves as the WE. In each measurement of capacitance, WE was applied with bias of 0.6 V or 0.7 V vs. Ag/AgCl, and the frequency range was 0.1 Hz–10 kHz. A Randles circuit model $R_s + R_p/CPE$ was used to fit the curves and to extract the capacitance. In this circuit, R_s is the resistance of active electrolyte, R_p represents the resistance in charge transfer, and CPE is a constant phase element.

Grazing-incidence wide-angle X-ray scattering

GIWAXS experiments were performed following the reported procedure.⁴⁸ All samples for GIWAXS measurements were deposited on cut silicon wafers and had a thickness of about 100 nm. They were measured at BeamLine 9A in the Pohang Accelerator Laboratory in South Korea. The X-ray energy was 11.08 eV and the incidence angle was 0.12°. Samples were measured in vacuum and the total exposure time was 10 s. The scattered X-rays were recorded by a charge-coupled device detector located 221.9351 mm from the sample.

OEETs, complementary inverters, and LIF neurons

OEETs were fabricated following a procedure reported previously.²⁶ Microscope glass slides were thoroughly cleaned *via* successive sonication in acetone, deionized water, and isopropanol, and then blown dry with nitrogen. Source/drain electrodes were thermally deposited with 5 nm Cr and 50 nm Au, and patterned with photolithography and wet etching. A first layer of parylene C (1 μm) was coated together with a drop of 3-(trimethoxysilyl) propyl methacrylate (A-174 Silane), to serve as an insulating layer between the metal electrode and the electrolyte. A dilution of industrial surfactant (2% Micro-90) was subsequently spin-coated before the depositing of a second layer (sacrificial layer) of parylene C (1 μm). To protect parylene



C layers from a subsequent plasma reactive ion etching step (150 W, O₂ = 500 sccm, CF₄ = 1000 sccm, 380 s), a thick positive photoresist (5 μm, AZ 10XT 520CP) was spin-coated on top of the parylene C layers. A second photolithographic patterning step followed by an application of AZ developer was carried out to define the contact pads and the OEET channels. The subsequent plasma reactive ion etching step was applied to indiscriminately remove the organic layers including photoresist and parylene C, until the contact pads and the OEET channel area were exposed to the air, while the other part of the device was still covered with two layers of parylene C. The channel between source and drain was patterned to be $W/L = 400 \mu\text{m}/6 \mu\text{m}$. The obtained OEET device was spin-coated with PBBT-H, PBBT-Me or BBL MSA solutions to form polymer film of 50 nm. After removing the residual MSA by immersing the device in deionized water, the polymer film was dried with nitrogen flow. The sacrificial layer of parylene C was peeled off, removing the polymer film on top of it and leaving the polymer in the patterned area, which was the OEET channel and the electrode pads. Thus, the source and the drain electrode were connected by a micrometer-scale piece of p-type or n-type polymer. For all OEETs, 0.1 M NaCl aqueous solution was used as the electrolyte, and an Ag/AgCl pellet (purchased from VWR) was used as the gate electrode. The complementary inverters were assembled by connecting a p-type (PBBT-H or PBBT-Me) OEET and an n-type (BBL) OEET with silver paste. The LIF neurons were assembled by connecting two p-type (PBBT-Me) OEET and three n-type (BBL) OEETs as shown in Fig. 6(a). For processing convenience of the LIF neuron, the channel width to length ratio is $W/L = 325/40 \mu\text{m}/\mu\text{m}$ for p-type OEETs and $W/L = 1300/40 \mu\text{m}/\mu\text{m}$ for n-type OEETs. The LIF neurons based on P(g₄2T-T) and BBL were assembled in a similar way, and W/L was the same. The devices were characterized with Keithley 4200A-SCS (with 4225-PMU Ultra Fast I-V Module and 4225-RPM Remote Amplifier/Switch Modules).

Conflicts of interest

C.-Y. Y., M.-A. S., and S. F. are the co-founder of n-Ink AB. The other authors declare no competing interests.

Acknowledgements

The authors thank Dr Zhixing Wu (Linköping U.) for help with TGA measurements. This work was financially supported by the Knut and Alice Wallenberg Foundation (2021.0058, 2022.0034, and WWSC), the Swedish Research Council (2020-03243, 2022-04053, and 2022-04553), the European Commission through the FET-OPEN project MITICS (GA-964677), and the Swedish Government Strategic Research Area in Materials Science on Functional Materials at Linköping University (Faculty Grant SFO-Mat-LiU 2009-00971). H. Y. Woo acknowledges the financial support from the National Research Foundation of Korea (2019R1A6A1A11044070, NRF2020M3H4A3081814).

References

- I. Bargigia, L. R. Savagian, A. M. Osterholm, J. R. Reynolds and C. Silva, *J. Am. Chem. Soc.*, 2021, **143**, 294–308.
- Z. Fan and J. Y. Ouyang, *Adv. Electron. Mater.*, 2019, **5**, 1800769.
- K. R. Li, Y. L. Shao, H. P. Yan, Z. Lu, K. J. Griffith, J. H. Yan, G. Wang, H. W. Fan, J. Y. Lu, W. Huang, B. Bao, X. L. Liu, C. Y. Hou, Q. H. Zhang, Y. G. Li, J. S. Yu and H. Z. Wang, *Nat. Commun.*, 2018, **9**, 4798.
- P. Lundberg, Y. Tsuchiya, E. M. Lindh, S. Tang, C. Adachi and L. Edman, *Nat. Commun.*, 2019, **10**, 5307.
- E. Macchia, R. A. Picca, K. Manoli, C. Di Franco, D. Blasi, L. Sarcina, N. Ditaranto, N. Cioffi, R. Osterbacka, G. Scamarcio, F. Torricelli and L. Torsi, *Mater. Horiz.*, 2020, **7**, 999–1013.
- L. Manjakkal, A. Pullanchiyodan, N. Yogeswaran, E. S. Hosseini and R. Dahiya, *Adv. Mater.*, 2020, **32**, 1907254.
- D. Moia, A. Giovannitti, A. A. Szumska, I. P. Maria, E. Rezasoltani, M. Sachs, M. Schnurr, P. R. F. Barnes, I. McCulloch and J. Nelson, *Energy Environ. Sci.*, 2019, **12**, 1349–1357.
- B. D. Paulsen, K. Tybrandt, E. Stavrinidou and J. Rivnay, *Nat. Mater.*, 2020, **19**, 13–26.
- R. A. Picca, K. Manoli, E. Macchia, L. Sarcina, C. Di Franco, N. Cioffi, D. Blasi, R. Osterbacka, F. Torricelli, G. Scamarcio and L. Torsi, *Adv. Funct. Mater.*, 2020, **30**, 1904513.
- D. Scheunemann, V. Vijayakumar, H. Y. Zeng, P. Durand, N. Leclerc, M. Brinkmann and M. Kemerink, *Adv. Electron. Mater.*, 2020, **6**, 2000218.
- S. Tang, A. Sandström, P. Lundberg, T. Lanz, C. Larsen, S. van Reenen, M. Kemerink and L. Edman, *Nat. Commun.*, 2017, **8**, 1190.
- S. van Reenen, R. A. J. Janssen and M. Kemerink, *Adv. Funct. Mater.*, 2015, **25**, 3066–3073.
- A. V. Volkov, H. D. Sun, R. Kroon, T. P. Ruoko, C. Y. Che, J. Edberg, C. Muller, S. Fabiano and X. Crispin, *ACS Appl. Energy Mater.*, 2019, **2**, 5350–5355.
- H. M. Wang, Y. F. Diao, Y. Lu, H. R. Yang, Q. J. Zhou, K. Chruslki and J. M. D'Arcy, *Nat. Commun.*, 2020, **11**, 3882.
- C. C. Yu, C. Y. Wang, X. Liu, X. T. Jia, S. Naficy, K. W. Shu, M. Forsyth and G. G. Wallace, *Adv. Mater.*, 2016, **28**, 9349–9355.
- E. Zeglio, A. L. Rutz, T. E. Winkler, G. G. Malliaras and A. Herland, *Adv. Mater.*, 2019, **31**, 1806712.
- X. N. Zhang, B. H. Wang, L. Z. Huang, W. Huang, Z. Wang, W. G. Zhu, Y. Chen, Y. L. Mao, A. Facchetti and T. J. Marks, *Sci. Adv.*, 2020, **6**, eaaz1042.
- B. D. Paulsen, S. Fabiano and J. Rivnay, *Annu. Rev. Mater. Res.*, 2021, **51**, 73–99.
- J. Rivnay, S. Inal, A. Salleo, R. M. Owens, M. Berggren and G. G. Malliaras, *Nat. Rev. Mater.*, 2018, **3**, 17086.
- D. Ohayon, G. Nikiforidis, A. Savva, A. Giugni, S. Wustoni, T. Palanisamy, X. X. Chen, I. P. Maria, E. Di Fabrizio, P. Costa, I. McCulloch and S. Inal, *Nat. Mater.*, 2020, **19**, 456–463.



- 21 J. Chen, W. Huang, D. Zheng, Z. Xie, X. Zhuang, D. Zhao, Y. Chen, N. Su, H. Chen, R. M. Pankow, Z. Gao, J. Yu, X. Guo, Y. Cheng, J. Strzalka, X. Yu, T. J. Marks and A. Facchetti, *Nat. Mater.*, 2022, **21**, 564–571.
- 22 C. Liao, C. Mak, M. Zhang, H. L. Chan and F. Yan, *Adv. Mater.*, 2015, **27**, 676–681.
- 23 P. Andersson Ersman, R. Lassnig, J. Strandberg, D. Tu, V. Keshmiri, R. Forchheimer, S. Fabiano, G. Gustafsson and M. Berggren, *Nat. Commun.*, 2019, **10**, 5053.
- 24 P. C. Harikesh, C.-Y. Yang, D. Tu, J. Y. Gerasimov, A. M. Dar, A. Armada-Moreira, M. Massetti, R. Kroon, D. Bliman, R. Olsson, E. Stavrinidou, M. Berggren and S. Fabiano, *Nat. Commun.*, 2022, **13**, 901.
- 25 T. Sarkar, K. Lieberth, A. Pavlou, T. Frank, V. Mailaender, I. McCulloch, P. W. M. Blom, F. Torricelli and P. Gkoupidenis, *Nat. Electron.*, 2022, **5**, 774–783.
- 26 P. C. Harikesh, C.-Y. Yang, H.-Y. Wu, S. Zhang, M. J. Donahue, A. S. Caravaca, J.-D. Huang, P. S. Olofsson, M. Berggren, D. Tu and S. Fabiano, *Nat. Mater.*, 2023, **22**, 242–248.
- 27 J. Y. Gerasimov, R. Gabrielsson, R. Forchheimer, E. Stavrinidou, D. T. Simon, M. Berggren and S. Fabiano, *Adv. Sci.*, 2019, **6**, 1801339.
- 28 J. Y. Gerasimov, D. Zhao, A. Sultana, T. Abrahamsson, S. Han, D. Bliman, D. Tu, D. T. Simon, R. Olsson, X. Crispin, M. Berggren and S. Fabiano, *Adv. Electron. Mater.*, 2021, **7**, 2001126.
- 29 S. K. Lee, Y. W. Cho, J. S. Lee, Y. R. Jung, S. H. Oh, J. Y. Sun, S. Kim and Y. C. Joo, *Adv. Sci.*, 2021, **8**, 2001544.
- 30 W. Wang, Y. Jiang, D. Zhong, Z. Zhang, S. Choudhury, J. C. Lai, H. Gong, S. Niu, X. Yan, Y. Zheng, C. C. Shih, R. Ning, Q. Lin, D. Li, Y. H. Kim, J. Kim, Y. X. Wang, C. Zhao, C. Xu, X. Ji, Y. Nishio, H. Lyu, J. B. H. Tok and Z. Bao, *Science*, 2023, **380**, 735–742.
- 31 S. Wang, X. Chen, C. Zhao, Y. Kong, B. Lin, Y. Wu, Z. Bi, Z. Xuan, T. Li, Y. Li, W. Zhang, E. Ma, Z. Wang and W. Ma, *Nat. Electron.*, 2023, **6**, 281–291.
- 32 Y. Zhang, E. R. W. van Doremaele, G. Ye, T. Stevens, J. Song, R. C. Chiechi and Y. van de Burgt, *Adv. Mater.*, 2022, **34**, e2200393.
- 33 J. Y. Gerasimov, D. Tu, V. Hitaishi, P. C. Harikesh, C. Y. Yang, T. Abrahamsson, M. Rad, M. J. Donahue, M. S. Ejneby, M. Berggren, R. Forchheimer and S. Fabiano, *Adv. Sci.*, 2023, **10**, e2207023.
- 34 X. Ji, B. D. Paulsen, G. K. K. Chik, R. Wu, Y. Yin, P. K. L. Chan and J. Rivnay, *Nat. Commun.*, 2021, **12**, 2480.
- 35 S. Pecqueur, M. Mastropasqua Talamo, D. Guérin, P. Blanchard, J. Roncali, D. Vuillaume and F. Alibert, *Adv. Electron. Mater.*, 2018, **4**, 1800166.
- 36 L. Liu, W. Xu, Y. Ni, Z. Xu, B. Cui, J. Liu, H. Wei and W. Xu, *ACS Nano*, 2022, **16**, 2282–2291.
- 37 Y. Ni, H. Han, J. Liu, Y. Choi, L. Liu, Z. Xu, L. Yang, C. Jiang, W. Gao and W. Xu, *Nano Energy*, 2022, **104**, 107898.
- 38 H. Wei, Y. Ni, L. Sun, H. Yu, J. Gong, Y. Du, M. Ma, H. Han and W. Xu, *Nano Energy*, 2021, **81**, 105648.
- 39 S. Zhang, J. Guo, L. Liu, H. Ruan, C. Kong, X. Yuan, B. Zhang, G. Gu, P. Cui, G. Cheng and Z. Du, *Nano Energy*, 2022, **91**, 106660.
- 40 Y. Peng, L. Gao, C. Liu, J. Deng, M. Xie, L. Bai, G. Wang, Y. Cheng, W. Huang and J. Yu, *Nano Res.*, 2023, DOI: [10.1007/s12274-023-5633-y](https://doi.org/10.1007/s12274-023-5633-y).
- 41 G. D. Spyropoulos, J. N. Gelinis and D. Khodagholy, *Sci. Adv.*, 2019, **5**, eaau7378.
- 42 J. Rivnay, P. Leleux, M. Sessolo, D. Khodagholy, T. Herve, M. Flocchi and G. G. Malliaras, *Adv. Mater.*, 2013, **25**, 7010.
- 43 D. Khodagholy, J. Rivnay, M. Sessolo, M. Gurfinkel, P. Leleux, L. H. Jimison, E. Stavrinidou, T. Herve, S. Sanaur, R. M. Owens and G. G. Malliaras, *Nat. Commun.*, 2013, **4**, 2133.
- 44 J. Rivnay, P. Leleux, M. Ferro, M. Sessolo, A. Williamson, D. A. Koutsouras, D. Khodagholy, M. Ramuz, X. Strakosas, R. M. Owens, C. Benar, J. M. Badier, C. Bernard and G. G. Malliaras, *Sci. Adv.*, 2015, **1**, e1400251.
- 45 S. M. Kim, C. H. Kim, Y. Kim, N. Kim, W. J. Lee, E. H. Lee, D. Kim, S. Park, K. Lee, J. Rivnay and M. H. Yoon, *Nat. Commun.*, 2018, **9**, 3858.
- 46 C. Y. Yang, D. Tu, T. P. Ruoko, J. Y. Gerasimov, H. Y. Wu, P. C. Harikesh, M. Massetti, M. A. Stoeckel, R. Kroon, C. Muller, M. Berggren and S. Fabiano, *Adv. Electron. Mater.*, 2022, **8**, 2100907.
- 47 Y. Yao, W. Huang, J. Chen, G. Wang, H. Chen, X. Zhuang, Y. Ying, J. Ping, T. J. Marks and A. Facchetti, *Proc. Natl. Acad. Sci. U. S. A.*, 2021, **118**, e2111790118.
- 48 H. Y. Wu, C. Y. Yang, Q. F. Li, N. B. Kolhe, X. Strakosas, M. A. Stoeckel, Z. Wu, W. L. Jin, M. Savvakis, R. Kroon, D. Y. Tu, H. Y. Woo, M. Berggren, S. A. Jenekhe and S. Fabiano, *Adv. Mater.*, 2022, **34**, 2106235.
- 49 R. B. Rashid, W. Y. Du, S. Griggs, I. P. Maria, I. McCulloch and J. Rivnay, *Sci. Adv.*, 2021, **7**, eabh1055.
- 50 X. Ji, X. Lin and J. Rivnay, *Nat. Commun.*, 2023, **14**, 1665.
- 51 H. D. Sun, M. Vagin, S. H. Wang, X. Crispin, R. Forchheimer, M. Berggren and S. Fabiano, *Adv. Mater.*, 2018, **30**, 1704916.
- 52 W. Huang, J. H. Chen, Y. Yao, D. Zheng, X. D. Ji, L. W. Feng, D. Moore, N. R. Glavin, M. Xie, Y. Chen, R. M. Pankow, A. Surendran, Z. Wang, Y. Xia, L. B. Bai, J. Rivnay, J. F. Ping, X. G. Guo, Y. H. Cheng, T. J. Marks and A. Facchetti, *Nature*, 2023, **613**, 496.
- 53 P. Y. Li, J. W. Shi, Y. Q. Lei, Z. Huang and T. Lei, *Nat. Commun.*, 2022, **13**, 5970.
- 54 S. Zhang, P. Ding, T. P. Ruoko, R. Wu, M. A. Stoeckel, M. Massetti, T. Liu, M. Vagin, D. Meli, R. Kroon, J. Rivnay and S. Fabiano, *Adv. Funct. Mater.*, 2023, DOI: [10.1002/adfm.202302249](https://doi.org/10.1002/adfm.202302249).
- 55 X. Y. Luo, H. G. Shen, K. Perera, D. T. Tran, B. W. Boudouris and J. G. Mei, *ACS Macro Lett.*, 2021, **10**, 1061–1067.
- 56 A. Giovannitti, R. B. Rashid, Q. Thiburce, B. D. Paulsen, C. Cendra, K. Thorley, D. Moia, J. T. Mefford, D. Hanifi, W. Y. Du, M. Moser, A. Salleo, J. Nelson, I. McCulloch and J. Rivnay, *Adv. Mater.*, 2020, **32**, 1908047.
- 57 T. C. H. Castillo, M. Moser, C. Cendra, P. D. Nayak, A. Salleo, I. McCulloch and S. Inal, *Chem. Mater.*, 2022, **34**, 6723.
- 58 A. Sava, R. Hallani, C. Cendra, J. Surgailis, T. C. Hidalgo, S. Wustoni, R. Sheelamanthula, X. X. Chen, M. Kirkus,



- A. Giovannitti, A. Salleo, I. McCulloch and S. Inal, *Adv. Funct. Mater.*, 2020, **30**, 1907657.
- 59 M. Moser, T. C. Hidalgo, J. Surgailis, J. Gladisch, S. Ghosh, R. Sheelamanthula, Q. Thiburce, A. Giovannitti, A. Salleo, N. Gasparini, A. Wadsworth, I. Zozoulenko, M. Berggren, E. Stavrinidou, S. Inal and I. McCulloch, *Adv. Mater.*, 2020, **32**, 2002748.
- 60 K. Xu, T. P. Ruoko, M. Shokrani, D. Scheunemann, H. Abdalla, H. Sun, C. Y. Yang, Y. Puttisong, N. B. Kolhe, J. S. M. Figueroa, J. O. Pedersen, T. Ederth, W. M. Chen, M. Berggren, S. A. Jenekhe, D. Fazzi, M. Kemerink and S. Fabiano, *Adv. Funct. Mater.*, 2022, **32**, 2112276.
- 61 S. Wang, H. Sun, U. Ail, M. Vagin, P. O. Persson, J. W. Andreasen, W. Thiel, M. Berggren, X. Crispin, D. Fazzi and S. Fabiano, *Adv. Mater.*, 2016, **28**, 10764–10771.
- 62 S. T. Wang, W. Hong, S. D. Ren, J. Li, M. Wang, X. K. Gao and H. X. Li, *J. Polym. Sci., Part A: Polym. Chem.*, 2012, **50**, 4272–4276.
- 63 X. H. Wu, T. L. D. Tam, S. Chen, T. Salim, X. M. Zhao, Z. L. Zhou, M. Lin, J. W. Xu, Y. L. Loo and W. L. Leong, *Adv. Mater.*, 2022, **34**, 2206118.
- 64 T. L. D. Tam, M. Lin, S. W. Chien and J. W. Xu, *ACS Macro Lett.*, 2022, **11**, 110–115.
- 65 S. L. Zhang, M. Massetti, T. P. Ruoko, D. Y. Tu, C. Y. Yang, X. J. Liu, Z. A. Wu, Y. Lee, R. Kroon, P. O. A. Persson, H. Y. Woo, M. Berggren, C. Muller, M. Fahlman and S. Fabiano, *Adv. Funct. Mater.*, 2022, **32**, 2106447.
- 66 E. Stein, O. Nahor, M. Stolov, V. Freger, I. M. Petruta, I. McCulloch and G. L. Frey, *Nat. Commun.*, 2022, **13**, 5548.
- 67 J. J. Song, H. Liu, Z. Y. Zhao, X. Y. Guo, C. K. Liu, S. Griggs, A. Marks, Y. Zhu, H. K. W. Law, I. McCulloch and F. Yan, *Sci. Adv.*, 2023, **9**, eadd9627.
- 68 J. J. Samuel, A. Garudapalli, A. A. Mohapatra, C. Gangadharappa, S. Patil and N. P. B. Aetukuri, *Adv. Funct. Mater.*, 2021, **31**, 2102903.
- 69 P. Romele, M. Ghittorelli, Z. M. Kovacs-Vajna and F. Torricelli, *Nat. Commun.*, 2019, **10**, 3044.
- 70 E. Surmiak, A. Twarda-Clapa, K. M. Zak, B. Musielak, M. D. Tomala, K. Kubica, P. Grudnik, M. Madej, M. Jablonski, J. Potempa, J. Kalinowska-Tluscik, A. Domling, G. Dubin and T. A. Holak, *ACS Chem. Biol.*, 2016, **11**, 3310–3318.
- 71 C. P. Wong, H. Ohnuma and G. C. Berry, *J. Polym. Sci., Part C: Polym. Symp.*, 1978, **65**, 173–192.
- 72 G. Berry and S. Yen, in *Addition and Condensation Polymerization Processes*, ed. N. A. J. Platzer, American Chemical Society, Washington, D.C., 1st edn, 1969, vol. 91, ch. 48, pp. 734–756.

