




Cite this: *J. Mater. Chem. C*, 2023, 11, 8154

Impact of two diammonium cations on the structure and photophysics of layered Sn-based perovskites†

Eelco K. Tekelenburg,  Nawal Aledlbi, Lijun Chen, Graeme R. Blake  and Maria A. Loi *

Layered metal-halide perovskites have shown great promise for applications in optoelectronic devices, where a large number of suitable organic cations give the opportunity to tune their structural and optical properties. However, especially for Sn-based perovskites, a detailed understanding of the impact of the cation on the crystalline structure is still missing. By employing two cations, 2,2'-oxybis(ethylammonium) (OBE) and 2,2'-(ethylenedioxy)bis(ethylammonium) (EDBE), we obtain a planar (100) and a corrugated (110)-oriented perovskite, respectively, where the hydrogen bonding between the EDBE cations stabilises the corrugated structure. OBESnI₄ exhibits a relatively narrow band gap and photoluminescence bands compared to EDBESnI₄. In-depth analysis shows that the markedly different optical properties of the two compounds have an extrinsic origin. Interestingly, thin films of OBESnI₄ can be obtained both in black and red colours. This effect is attributed to a second crystalline phase that can be obtained by processing the thin films at 100 °C. Our work highlights that the design of the crystal structure as obtained by ligand chemistry can be used to obtain the desired optical properties, whereas thin film engineering can result in multiple crystalline phases unique to Sn-based perovskites.

Received 31st October 2022,
Accepted 4th January 2023

DOI: 10.1039/d2tc04626a

rsc.li/materials-c

10th Anniversary Statement written by Maria A. Loi

I was a young post-doctoral fellow when, at that time Journal Material Chemistry, published my work on the photophysics and solar cells of phthalocyanine-fulleropyrrolidine dyads and devoted the cover to the article. From that moment, I have been always considering the Journal Material Chemistry family, and especially Journal Material Chemistry C, as the perfect avenue for multidisciplinary works where new materials, deep spectroscopical investigation and even device investigations can be presented to a multifaceted community. The interdisciplinarity, breadth and plasticity in embracing the newest topics emerging from the community are the characteristics, that in my opinion, determine the continuous success of Journal Material Chemistry C. Now Journal Material Chemistry C is 10 years old but does not give any signs of ageing or rigidity. As modern science is highly accelerated, this is a merit of the team running the journal. Happy birthday to Journal Material Chemistry C, wishing it many years of youth ahead.

Introduction

Layered metal-halide perovskites are at the forefront of emerging light-emitting materials and already have proven their invaluable contributions to photovoltaic devices and light-emitting diodes.^{1–3} This class of materials offers a vast amount of different crystal structures due to its flexibility to accommodate a large number of organic cations.^{2,4} Of the large organic cations used, most reports focus on monoammonium cations

such as butylammonium and phenethylammonium. Recently, diammonium cations are gaining momentum because of the hope to obtain different functionalities, and the power conversion efficiency of solar cells is increasing using diammonium cations.⁵ These structures show exotic phenomena, enabling the design of materials that emit either narrow or broad photoluminescence (PL) bands.^{6,7}

The origin of the optical properties of layered perovskites lies in the connectivity of the inorganic framework, where we can distinguish two main types: the (100)- and the (110)-oriented perovskites.^{8,9} These structures can be envisioned as slices of the cubic perovskite structure along the (100) or the (110) crystallographic planes and are separated by organic cations. For this reason, the (100)-type consists of flat layers of corner-shared inorganic octahedra with metal-halide-metal

Zernike Institute for Advanced Materials, University of Groningen, Nijenborgh 4, 9747 AG, Groningen, The Netherlands. E-mail: m.a.loi@rug.nl

† Electronic supplementary information (ESI) available: Experimental details, further experimental data, photoluminescence spectroscopy, structural parameters. CCDC 2204974 and 2204975. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d2tc04626a>



angles close to 180° , while the $\langle 110 \rangle$ -type consists of corrugated sheets with angles close to 90° among inorganic octahedra. Interestingly, the vast majority of layered metal halide perovskites adopt the $\langle 100 \rangle$ -type structure, and it remains challenging to predict which cations can favour $\langle 110 \rangle$ -type structures.¹⁰ However, from empirical studies, it is clear that cation size and intercation interactions (through halide or hydrogen bonding) are important factors that stabilise the $\langle 110 \rangle$ -type.^{9–11}

Owing to the pioneering work by Dohner *et al.*, the optical properties of a number of $\langle 110 \rangle$ perovskites were investigated, of which some compounds employed 2,2'-(ethylenedioxy)bis(ethylammonium) (EDBE).^{11,12} It was shown that the band gap of $\langle 110 \rangle$ perovskites is typically wider than the $\langle 100 \rangle$ counterpart, where some of the $\langle 110 \rangle$ perovskites showed broad emission bands attributed to the emission from self-trapped excitons. These works inspired further exploration and a number of other $\langle 110 \rangle$ perovskites have been reported since.^{2,13,14} It is not known if the length of the EDBE cation is important to stabilise this structure. In addition, a survey through the $\langle 110 \rangle$ perovskites shows that most of the compounds contain Pb, whereas very little has been done with the environmentally more benign Sn. In particular, much is unknown about the optical properties of these Sn-based perovskites and remains to be explored.

Layered Sn-based perovskites have shown intriguing structural flexibility where the same organic cations result in two distinct crystalline structures.^{15–17} For example, Mao *et al.* found that the kinetic product of the synthesis in hydroiodic acid formed red crystals of the $\langle 110 \rangle$ type, while the thermodynamically stable black crystals crystallised in the $\langle 100 \rangle$ type.¹⁵ However, thus far, only structural isomers were found for single crystals, yet applying them in thin films could open new pathways to tune the optoelectronic properties of these materials in device applications.

In this report, we address the need to comprehend the structure and optical properties of layered Sn-based perovskites, where we systematically investigate two diammonium organic cations that vary in length: 2,2'-oxybis(ethylammonium) (OBE) and 2,2'-(methylenedioxy)bis(ethylammonium) (EDBE). A marked contrast is obtained as OBESnI₄ forms a $\langle 100 \rangle$ -oriented perovskite with relatively narrow emission peaks compared to the broad emission obtained with the $\langle 110 \rangle$ -oriented EDBESnI₄. We show through temperature and power-dependent photoluminescence measurements that the low-energy emission in these compounds is extrinsic in nature. These compositions were successfully fabricated into thin films by a blade-coating deposition process. Furthermore, we reveal that the annealing temperature of the thin films of OBESnI₄ drastically changes the colour of the films from black to red. This change in colour originates from a new crystalline phase marking the structural and optical flexibility of layered Sn-based perovskites.

Results and discussion

We synthesised mm-sized single crystals of OBESnI₄ and EDBESnI₄ using an Anti-Solvent Vapour Crystallisation method,

see ESI† for the details. A striking colour difference is seen for the two crystals: black-brown for OBESnI₄ and orange-red for EDBESnI₄, as shown in Fig. 1(a and b). We used X-ray diffraction (XRD) to unravel their crystal structures, which are depicted in Fig. 1(c and d) for OBESnI₄ and EDBESnI₄, respectively. Both structures were solved in the $P2_1/c$ space group (structural parameters are shown in Table S1, ESI†), although two types of structures were formed. OBESnI₄ consists of planar inorganic sheets separated by the diammonium cation, forming a $\langle 100 \rangle$ -type layered structure. In contrast, EDBESnI₄ forms corrugated sheets of the $\langle 110 \rangle$ type, where the inorganic octahedra are linked to each other with angles close to 90° . It is remarkable that a small difference in the cation length can induce such large differences in the structure. A further examination of the structure revealed that hydrogen bonds are formed between EDBE cations, see the inset of Fig. 1(d), which are absent in OBESnI₄. Hence, the additional length of the EDBE cation is of key importance to form these hydrogen bonds, which subsequently stabilise the corrugated structure.¹²

To further investigate the impact of the structure on the optical properties, we measured the Kubelka–Munk transformed diffuse reflectance $F(R)$ and PL spectra of the two compounds at room temperature (Fig. 1(e and f)). In line with the colour difference, EDBESnI₄ shows an absorption peak at 2.36 eV, a much higher value than the 1.99 eV for OBESnI₄. This large difference can be readily understood by considering the octahedral connectivity and the band edge orbitals of the compounds. Due to the antibonding character of both the valence (Sn 5s and I 5p) and conduction (Sn 5p and I 5p) band edge, the Sn–I–Sn angle has a major impact on the electronic and optical band gap.¹⁸ The close to 90° angles between octahedra in EDBESnI₄ decrease the orbital overlap, resulting in a widening of the band gap compared to OBESnI₄.¹⁶

The PL spectra of the two compounds exhibit different features. The PL of OBESnI₄ shows two peaks at 1.90 eV and 1.96 eV relatively close to the absorption edge. The relative intensity of the two peaks varies across the samples (Fig. S1(a), ESI†), and the high-energy peak becomes the dominant emission at high excitation fluences as the low-energy emission saturates (Fig. S1(b), ESI†), which suggests that the low-energy emission has an extrinsic origin, *i.e.* emission from defects. The PL of EDBESnI₄ shows a broad emission band at 1.61 eV with a Stokes shift of ≈ 700 meV, the first report on such a Sn-based system. Interestingly, the related Pb-based EDBEPbI₄ shows a much narrower emission that shows features closely resembling OBESnI₄,^{11,19} while broad emissions are more commonly observed for bromide and chloride containing systems.²⁰ To test the stability of our compounds, we measured the PL spectra by continuously illuminating the samples with our laser for 10 minutes in a nitrogen environment, as shown in Fig. S7 (ESI†). Only minor fluctuations in intensity are observed, indicating that our Sn-based layered structures show good stability.

To further understand the optical properties of these systems, temperature-dependent PL spectra of the single crystals were measured and are shown in Fig. 2(a). We will start the discussion with OBESnI₄, for which three interesting observations



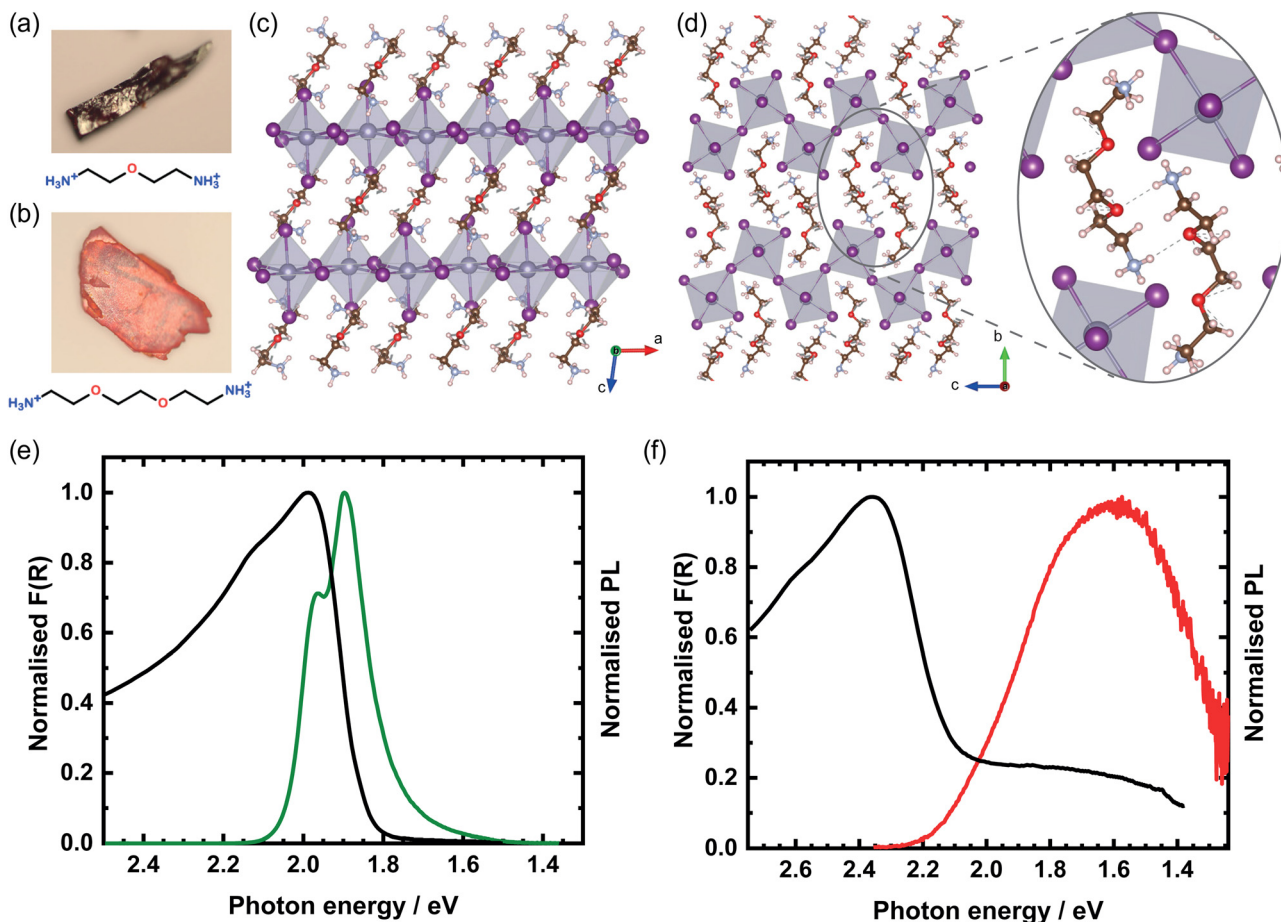


Fig. 1 (a) OBESnI₄ and (b) EDBESnI₄ images of mm-sized single crystals. Crystal structure of (c) OBESnI₄ and (d) EDBESnI₄, where grey atoms are Sn, purple are I, blue are N, brown are C, red are O, and white are H. The inset highlights the formed hydrogen bonds. Kubelka–Munk transformed diffuse reflectance and photoluminescence spectra of (e) OBESnI₄ and (f) EDBESnI₄.

can be made. (i) The emission at 1.90 eV disappears when cooling. This indicates that the low-energy emission is a thermally activated process. *Vice versa*, when the temperature is increased, the low-energy emission becomes more dominant underlining the presence of an energy barrier for this emission (Fig. S2, ESI†). A phase transition is excluded as we did not observe any appreciable change in the XRD from 100 K to 370 K. The disappearance of the low-energy peak in our diammonium compound is unique and contrasts with the appearance of a low-energy peak typically seen for monoammonium cations forming (100)-oriented perovskites.^{21,22} (ii) A blue shift is observed for the high-energy PL peak. This blue shift is unusual for metal-halide perovskites as generally the photoluminescence redshifts due to the contraction of the lattice (increasing orbital overlap) at lower temperatures. Although unusual, the overlapping tails of the absorbance and the photoluminescence in tandem with a reduced exciton-phonon coupling could cause a blue shift.²³ (iii) At 4.4 K, a substructure in the PL spectra is seen with two additional shoulders towards lower energy. Only at this low temperature, the shoulders are clearly visible as for higher temperatures the thermal energy can dissociate these bound states (see Fig. S3, ESI†). These shoulders are investigated in greater detail through fluence-dependent PL spectroscopy, as shown in

Fig. 2(b). An increase of the excitation fluence over two orders of magnitude clearly shows that the relative contribution of the low-energy shoulders decreases with respect to the main peak at 2.04 eV. The approximate linear dependence of the 2.04 eV peak as a function of the excitation fluence is evidence of the free-excitonic nature of this emission, while the shoulder at 1.97 eV shows a sublinear dependence, hereby further supporting the extrinsic nature of these bound states.^{24,25}

For EDBESnI₄, as shown in Fig. 2(a), two evident PL peaks are seen when the temperature is lowered. We note that others only observed a single broad emission band in related Pb-based systems down to 150 K.¹¹ The PL peaks, approximately at 1.4 eV and 1.8 eV, show a non-monotonic increase of the intensity upon decreasing the temperature (Fig. S4, ESI†), where the intensity of the peaks at 1.4 eV and 1.8 eV maximise at 30 K and 80 K, respectively. In addition, the PL lifetime of the peaks extends into the μ s range at cryogenic temperatures (Fig. S5, ESI†). These observations closely resemble the intricate interplay of low-energy PL bands we reported on layered Pb-based perovskites and suggest that the main contribution to the emission stems from defects.²⁶ This view is supported by the sublinear dependence of the PL intensity at 4.5 K, as shown in



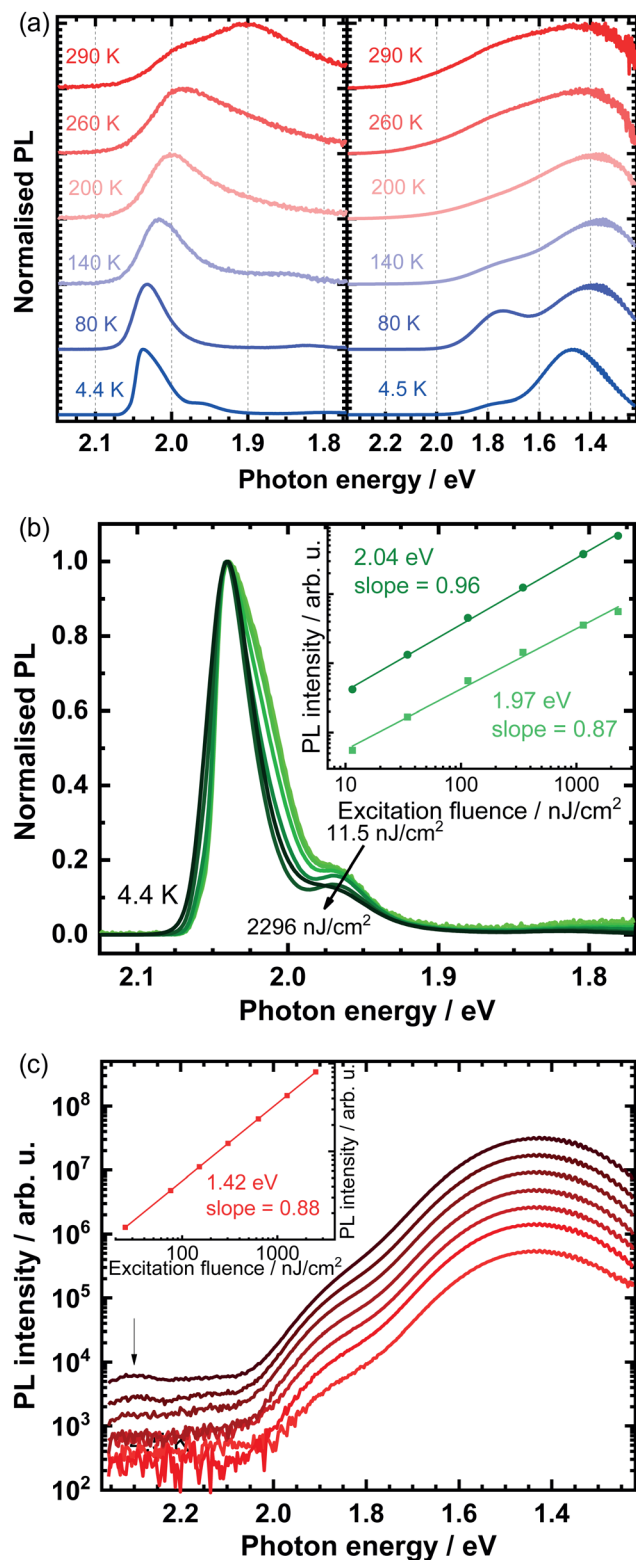


Fig. 2 (a) Temperature-dependent photoluminescence spectra of OBESnI₄ (left panel) and EDBESnI₄ (right panel). Power-dependent photoluminescence spectra at 4.4 K of (b) OBESnI₄ and (c) EDBESnI₄, where the insets show the double-logarithmic plots of the photoluminescence intensity versus excitation fluence.

Fig. 2(c). We note that at high fluences additional resonances are observed at approximately 2.3 eV, indicated by the arrow in Fig. 2(c).

Broad emission bands have been observed in a variety of structures, such as $\langle 100 \rangle$, $\langle 110 \rangle$, and 0D perovskites.^{7,20} The origin of this emission is under intense debate and is dependent on the crystal structure as well as its elemental composition. For instance, for $\langle 100 \rangle$ and $\langle 110 \rangle$ perovskites containing bromide and chloride, the broad emission has been shown to depend on the degree of distortion of the inorganic layers and was attributed to the emission of self-trapped excitons.^{11,27} In contrast, the emission from layered perovskites with iodine was ascribed to defects, where in the $\langle 110 \rangle$ perovskite EDBEPbI₄ colour centres were formed out of iodine interstitials.^{19,26} All of these works have focused on Pb-based perovskites; it is with our work that we provide evidence that corrugated tin-iodide perovskites also have broad emission bands stemming from an extrinsic origin, *i.e.* from defects. We note that this emission is from a different origin than the broad emission in 0D tin-iodide perovskites. These 0D compounds have a high PL quantum yield owing to the emission from self-trapped excitons localised on the isolated inorganic octahedra.^{28,29}

To conclude this section, we have shown that the structure of layered perovskites can be tailored by the choice of the organic cation. Critical for the stabilisation of the corrugated $\langle 110 \rangle$ structure is that EDBe can form hydrogen bonds between cations, while the smaller OBE does not form hydrogen bonds and crystallises in the $\langle 100 \rangle$ -oriented perovskite. Both compounds showed photoluminescence with unusual features for Sn-based perovskites, where we discussed that the temperature plays a decisive role to observe the extrinsic nature of low-energy resonances.

Naturally, the use of OBESnI₄ in devices will require thin films fabricated in a scalable manner. Hence, thin films were blade coated as detailed in the ESI† and are shown in Fig. 3(a). We chose 70 °C and 100 °C as these values are typical annealing temperatures for perovskite solar cells. In addition, this allowed us to study the thin films in two cases where the crystallisation rate would change significantly. The films exhibited an unusual colour change depending on the processing temperature. For the black film, a temperature of 70 °C is used for both the doctor-blade stage and the successive annealing on a hotplate. For the red film in the middle, 100 °C is used for both processing steps. While for the film on the right, the blade coating was performed at 70 °C and the annealing on the hotplate at 100 °C. From hereon, we will refer to the films by their processing temperature for simplicity. Hence, an intriguing observation is made that the processing temperature drastically changes the optical properties of the film, where we stress that the same precursor solution was used for each of the films. To the best of our knowledge, this is the first time that such behaviour is reported in Sn-based layered perovskite thin films. We note that this temperature-dependent behaviour is exclusive to OBESnI₄ and is only observable during annealing when the films are still wet. Thus, heating of the fully solidified black films to 100 °C did not change the colour to red, in line with the absence of a phase transition in single crystals as discussed above.

The normalised absorbance spectra of the films are shown in Fig. 3(b). The absorbance peak of the 70 °C film at 1.98 eV matches well with the Kubelka–Munk transformed spectra



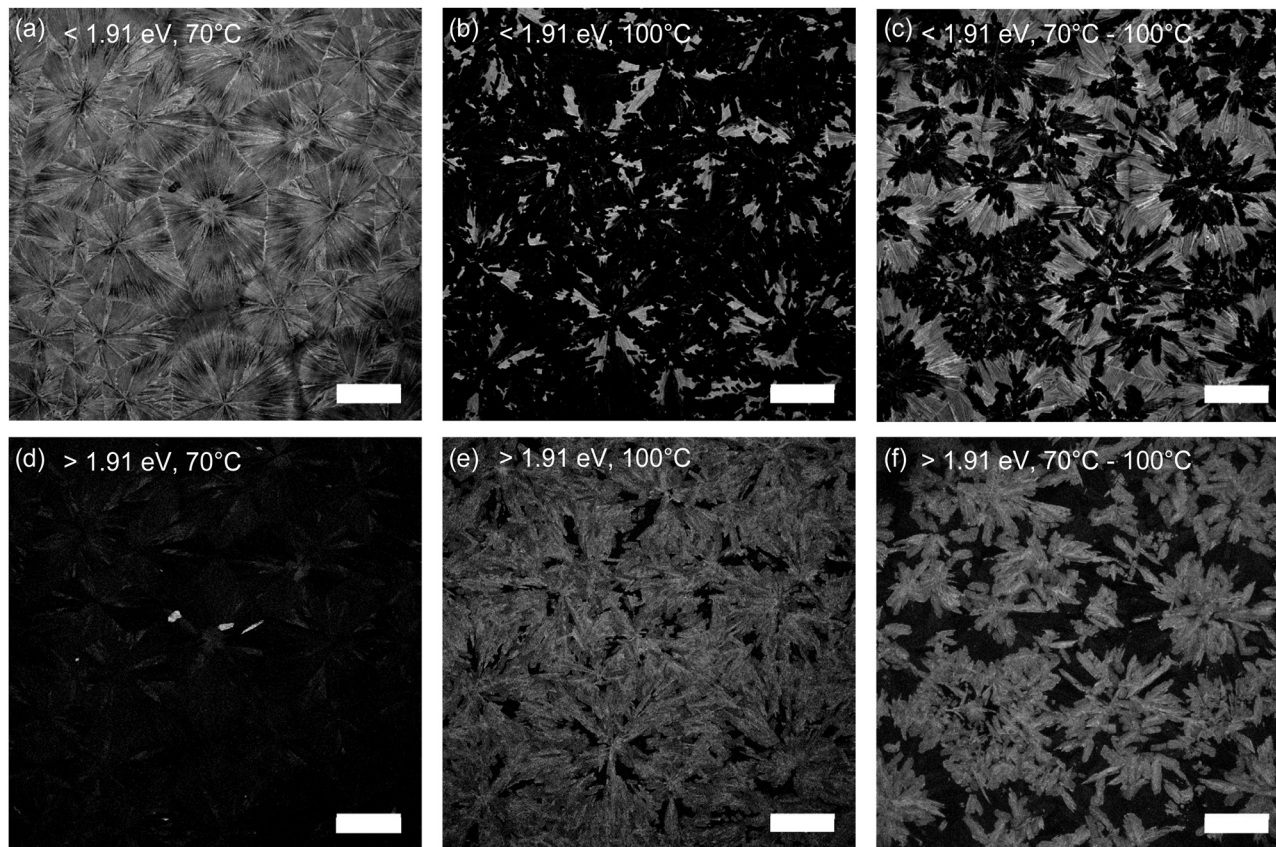


Fig. 4 Confocal photoluminescence micrographs in the range $< 1.91\text{ eV}$ (a–c) and $> 1.91\text{ eV}$ (d–f) for OBESnI_4 thin films processed at $70\text{ }^\circ\text{C}$, $100\text{ }^\circ\text{C}$, and $70\text{--}100\text{ }^\circ\text{C}$. Scale bar is $100\text{ }\mu\text{m}$.

as additional hydrogen bonds were formed between neighbouring organic cations. We investigated the optical properties of the new compounds, where OBESnI_4 showed two photoluminescence peaks of which the low-energy emission was thermally activated. In contrast, EDBe showed a broad emission band with multiple emissive states at low temperatures, where its fluence-dependent behaviour suggests an origin from defects. Strikingly, thin films of OBESnI_4 showed a contrasting change of colour from black to red when the processing temperature was increased from $70\text{ }^\circ\text{C}$ to $100\text{ }^\circ\text{C}$. The red colour stems from a new unidentified crystal phase that was well-separated from the black phase. With this work, we clarify how intercation interactions can result in two different types of layered perovskites with distinct optical properties, and we highlight that the processing conditions, typically used for device fabrication, have a drastic impact on the optical and structural properties of our newly reported compound.

Author contributions

E. K. T.: conceptualisation, investigation, writing – original draft N. A.: investigation, resources L. C.: resources G. R. B.: supervision, writing – review and editing, funding acquisition M. A. L. conceptualisation, supervision, writing – review and editing, funding acquisition.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

A. F. Kamp, T. Zaharia, and J. Baas are kindly acknowledged for their technical support. E. K. T. acknowledges the funding provided by the Zernike Institute of Advanced Materials – Bonus Incentive Scheme.

References

- 1 M. Pitaro, E. K. Tekelenburg, S. Shao and M. A. Loi, *Adv. Mater.*, 2022, **34**, 2105844.
- 2 X. Li, J. M. Hoffman and M. G. Kanatzidis, *Chem. Rev.*, 2021, **121**, 2230–2291.
- 3 A. Fakharuddin, U. Shabbir, W. Qiu, T. Iqbal, M. Sultan, P. Heremans and L. Schmidt-Mende, *Adv. Mater.*, 2019, **31**, 1807095.
- 4 B. Saparov and D. B. Mitzi, *Chem. Rev.*, 2016, **116**, 4558–4596.
- 5 S. Shao, X. Cui and Z. Li, *ACS Mater. Lett.*, 2022, **4**, 891–917.
- 6 C. Katan, N. Mercier and J. Even, *Chem. Rev.*, 2019, **119**, 3140–3192.



- 7 D. Cortecchia, J. Yin, A. Petrozza and C. Soci, *J. Mater. Chem. C*, 2019, **7**, 4956–4969.
- 8 D. B. Mitzi, C. A. Feild, W. T. A. Harrison and A. M. Guloy, *Nature*, 1994, **368**, 561–563.
- 9 D. B. Mitzi, S. Wang, C. A. Feild, C. A. Chess and A. M. Guloy, *Science*, 1995, **267**, 1473–1476.
- 10 Y. Y. Guo, J. A. McNulty, N. A. Mica, I. D. Samuel, A. M. Slawin, M. Bühl and P. Lightfoot, *Chem. Commun.*, 2019, **55**, 9935–9938.
- 11 E. R. Dohner, A. Jaffe, L. R. Bradshaw and H. I. Karunadasa, *J. Am. Chem. Soc.*, 2014, **136**, 13154–13157.
- 12 E. R. Dohner, E. T. Hoke and H. I. Karunadasa, *J. Am. Chem. Soc.*, 2014, **136**, 1718–1721.
- 13 X. Li, P. Guo, M. Kepenekian, I. Hadar, C. Katan, J. Even, C. C. Stoumpos, R. D. Schaller and M. G. Kanatzidis, *Chem. Mater.*, 2019, **31**, 3582–3590.
- 14 M. Ben, H. Salah, N. Mercier, M. Allain, A. Leblanc, J. Dittmer, C. Botta, C. Quarti and C. Katan, *Chem. Mater.*, 2022, **34**, 5780–5790.
- 15 L. Mao, H. Tsai, W. Nie, L. Ma, J. Im, C. C. Stoumpos, C. D. Malliakas, F. Hao, M. R. Wasielewski, A. D. Mohite and M. G. Kanatzidis, *Chem. Mater.*, 2016, **28**, 7781–7792.
- 16 C. C. Stoumpos, L. Mao, C. D. Malliakas and M. G. Kanatzidis, *Inorg. Chem.*, 2017, **56**, 56–73.
- 17 J. Guan, Z. Tang and A. M. Guloy, *Chem. Commun.*, 1999, 1833–1834.
- 18 J. L. Knutson, J. D. Martin and D. B. Mitzi, *Inorg. Chem.*, 2005, **44**, 4699–4705.
- 19 D. Cortecchia, S. Neutzner, A. R. S. Kandada, E. Mosconi, D. Meggiolaro, F. De Angelis, C. Soci and A. Petrozza, *J. Am. Chem. Soc.*, 2017, **139**, 39–42.
- 20 M. D. Smith and H. I. Karunadasa, *Acc. Chem. Res.*, 2018, **51**, 619–627.
- 21 G. C. Papavassiliou, I. B. Koutselas, D. J. Lagouvardos, J. Kapoutsis, A. Terzis and G. J. Papaioannou, *Mol. Cryst. Liq. Cryst. Sci. Technol., Sect. A*, 1994, **253**, 103–112.
- 22 G. Folpini, D. Cortecchia, A. Petrozza and A. R. Srimath Kandada, *J. Mater. Chem. C*, 2020, **8**, 10889–10896.
- 23 S. Wang, J. Ma, W. Li, J. Wang, H. Wang, H. Shen, J. Li, J. Wang, H. Luo and D. Li, *J. Phys. Chem. Lett.*, 2019, **10**, 2546–2553.
- 24 I. Pelant and J. Valenta, in *Luminescence Spectroscopy of Semiconductors*, Oxford University Press, 2012, ch. 3, pp. 82–97.
- 25 E. K. Tekelenburg, S. Kahmann, M. E. Kamminga, G. R. Blake and M. A. Loi, *Adv. Opt. Mater.*, 2021, **9**, 2001647.
- 26 S. Kahmann, E. K. Tekelenburg, H. Duim, M. E. Kamminga and M. A. Loi, *Nat. Commun.*, 2020, **11**, 2344.
- 27 M. D. Smith, A. Jaffe, E. R. Dohner, A. M. Lindenberg and H. I. Karunadasa, *Chem. Sci.*, 2017, **8**, 4497–4504.
- 28 C. Zhou, Y. Tian, Z. Yuan, H. Lin, B. Chen, R. Clark, T. Dilbeck, Y. Zhou, J. Hurley, J. Neu, T. Besara, T. Siegrist, P. Djurovich and B. Ma, *ACS Appl. Mater. Interfaces*, 2017, **9**, 44579–44583.
- 29 L.-J. Xu, H. Lin, S. Lee, C. Zhou, M. Worku, M. Chaaban, Q. He, A. Plaviak, X. Lin, B. Chen, M.-H. Du and B. Ma, *Chem. Mater.*, 2020, **32**, 4692–4698.
- 30 M. E. Kamminga, H. H. Fang, M. R. Filip, F. Giustino, J. Baas, G. R. Blake, M. A. Loi and T. T. Palstra, *Chem. Mater.*, 2016, **28**, 4554–4562.
- 31 S. Kahmann, H. Duim, A. J. Rommens, E. K. Tekelenburg, S. Shao and M. A. Loi, *Adv. Opt. Mater.*, 2021, **9**, 2100892.
- 32 C. M. Tsai, Y. P. Lin, M. K. Pola, S. Narra, E. Jokar, Y. W. Yang and E. W. G. Diau, *ACS Energy Lett.*, 2018, **3**, 2077–2085.

