



Cite this: *EES Catal.*, 2024, 2, 727

Cu-based catalysts for electrocatalytic nitrate reduction to ammonia: fundamentals and recent advances

Kouer Zhang,^a Yun Liu,^a Zhefei Pan,^{bc} Qing Xia,^a Xiaoyu Huo,^a Oladapo Christopher Esan,^a Xiao Zhang^{*a} and Liang An ^{*ad}

Electrocatalytic nitrate reduction has been identified as a promising technology for green ammonia production, allowing the conversion of harmful nitrate from wastewater into valuable ammonia using renewable electricity under ambient conditions. Developing advanced electrocatalysts is of paramount significance for improving the ammonia production efficiency in this process. Recently, Cu-based catalysts have been widely investigated in ammonia production *via* nitrate reduction due to their rapid reduction reaction kinetics, strong electrical conductivity, and ability to inhibit the hydrogen evolution reaction. Meanwhile, the reaction mechanism and computational and experimental methods have been extensively discussed to understand the theory behind the favourable properties of Cu-based catalysts. In this review, we focus on Cu-based catalysts, aiming to provide insights into the latest developments, reaction mechanisms, and state-of-the-art analysis methods for intermediates and products of nitrate reduction to ammonia. Future outlooks and remaining challenges are presented to provide guidance for advancing from experimental explorations to practical applications.

Received 3rd January 2024,
Accepted 3rd February 2024

DOI: 10.1039/d4ey00002a

rsc.li/eescatalysis


Broader context

The global demand for ammonia is significantly increasing due to its significant industrial value and great potential as an energy carrier. However, traditional chemical methods utilized for ammonia production contribute to high energy consumption, hydrogen consumption, and greenhouse gas emissions. Electrochemical nitrate reduction, powered by renewable electricity under ambient conditions, has emerged as a promising alternative technology for green ammonia production. Despite its potential, the efficiency of ammonia production in this process remains relatively low. Thus, extensive efforts have been undertaken to develop efficient electrocatalysts that can overcome this limitation. Among various metal-based catalysts, Cu-based catalysts have demonstrated significant potential, primarily due to their occupancy of d orbitals that closely resemble the lowest unoccupied π^* orbitals of nitrate. This unique characteristic facilitates accelerated electron transfer, leading to a reduced limiting potential and an expedited rate-determining step. In light of this, the present review aims to comprehensively explore the latest developments in Cu-based catalysts for electrocatalytic nitrate reduction to ammonia. This exploration will encompass an analysis of materials, elucidation of the underlying reaction mechanism, and evaluation of state-of-the-art analysis methods. By providing an up-to-date overview, this review ultimately intends to contribute to the advancement of future industrial implementations in this field.

1. Introduction

As a globally important ingredient for industry (fertilizer, high-value chemicals, and pharmaceutical) and a next-generation

energy carrier, ammonia (NH_3) has long been widely utilized.¹ In 2020, global ammonia demand reached 183 Mt with an expected increase of 20% in 2030.² Moreover, the overall ammonia demand is estimated to increase 3-to-4-fold to 560–665 Mt in 2050.³ Invented in 1909 by German chemists Fritz Haber and Carl Bosch, the Haber–Bosch process has long been known as the most common but impactful ammonia production method.⁴ In this process, ammonia is produced through a thermocatalytic reaction of nitrogen and hydrogen, as expressed in the equation below:



However, the traditional Haber–Bosch process is highly energy-sensitive, requiring high temperature (350–450 °C) and high

^a Department of Mechanical Engineering, The Hong Kong Polytechnic University, Hung Hom, Kowloon, Hong Kong SAR, China. E-mail: xiao1.zhang@polyu.edu.hk, liang.an@polyu.edu.hk

^b Key Laboratory of Low-Grade Energy Utilization Technologies and Systems (Chongqing University), Ministry of Education of China, Chongqing University, Chongqing 400044, China

^c Institute of Engineering Thermophysics, School of Energy and Power Engineering, Chongqing University, Chongqing 400044, China

^d Research Institute for Smart Energy, The Hong Kong Polytechnic University, Hun Hom, Kowloon, Hong Kong SAR, China



pressure (100–200 bar) to break the inert triple bond of nitrogen ($\text{N}\equiv\text{N}$) and promote the reaction rate.⁵ It is worth mentioning that the hydrogen (grey hydrogen) consumed in the Haber-Bosch process is produced through steam reforming, which converts methane (CH_4) to hydrogen and carbon monoxide (CO). This process requires high pressure (3–25 bar) and extremely high temperature (700–1000 °C).⁶ Thereafter, the carbon monoxide would undergo further treatment to be converted into carbon dioxide (CO_2). It is reported that the Haber-Bosch process accounts for over 1% of global annual energy consumption and produces over 1.4% of global CO_2 emission.^{7–9} Thus, tremendous efforts have been made to figure out an efficient and clean ammonia synthesis method. As a result, many alternative methods have been proposed in recent years, such as electrocatalysis, photocatalysis, heterogeneous catalysis, and nitrogenase enzyme catalysis.^{10,11}

Among them, electrocatalytic ammonia production in an aqueous system is currently a hot research area due to its potential for operating under ambient conditions, producing zero-emission, and using renewable energy as the driving force.^{12,13} With a flexible production scale, this method is suitable for combining intermittent renewable energy such as solar energy and wind energy.¹⁴ At first, researchers were interested in the nitrogen reduction reaction (NRR) due to its ability to directly utilize nitrogen and water. By utilizing water as an alternating hydrogen (H)-atom source, NRR avoids energy-intensive processes while solving the problem of hydrogen storage and transportation.¹⁵ Although this scenario is idealistic, the practical development of the NRR has long been impeded by low Faraday efficiency (FE, generally less than 10%) and a low ammonia yield rate (around 10^{-10} to 10^{-11} mol s^{-1}).¹⁶ This value is far below the target proposed by the U.S. Department of Energy (DOE), which is an FE of over 90% and an ammonia yield rate of over 10^{-6} mol s^{-1} .¹⁷ The poor performance of the NRR is mainly attributed to the inertness of $\text{N}\equiv\text{N}$ and low N_2 solubility in water (0.66 mmol L^{-1}).¹⁸ Moreover, it has been reported that false positives exist in some works due to contaminants from the environment and inaccuracies in production tests.¹⁹

The employment of the nitrate reduction reaction (NO_3RR) as a promising alternative to NRR for ammonia production is of great interest.²⁰ Compared with NRR, in NO_3RR , the solubility of nitrate (>2 mol L^{-1}) is much higher than that of nitrogen while the disassociation energy of $\text{N}=\text{O}$ (240 kJ mol^{-1}) is much lower than that of $\text{N}\equiv\text{N}$ (941 kJ mol^{-1}).^{21,22} In addition, NO_3RR is also an environmentally friendly nitrate degradation method as it converts harmful pollutants into valuable ammonia, realizing the concept of ‘turning waste into wealth’.^{23–25} However, the concerns regarding low product selectivity and sluggish reaction kinetics still exist, leading to unsatisfactory efficiency and impeding the further development of this method. To solve these problems, developing electrocatalysts with high activity and high selectivity is of top priority. Although precious metals and their alloys have been demonstrated to be effective for NO_3RR , their application in ammonia production is limited due to their scarcity and high cost.²³ Conversely, transition-metal catalysts have attracted much attention due to their adequate reserves and low cost. Besides, it is worth mentioning that the highly occupied d orbitals of some metals (Cu, Ag, Pt, *etc.*) are similar to the lowest unoccupied π^* orbital of nitrate, which can accelerate electron transfer on these metals.²⁴

Cu-based materials are one of the most promising types of catalysts for nitrate reduction and have been widely reported with superior performance recently.²⁶ In general, Cu-based catalysts show the lowest limiting potential and the fastest rate-determining step, indicating excellent thermodynamic and kinetic activity.^{27,28} Furthermore, Cu-based catalysts have a weak ability for hydrogen evolution and outstanding selectivity towards ammonia production.^{29–31} These distinctive characteristics of Cu-based catalysts play a crucial role in enhancing the efficiency of electrocatalytic ammonia production, thereby underscoring the indispensable role of Cu in this field.

This review is primarily centered on Cu-based catalysts for the reduction of nitrate to ammonia, examining both the fundamental principles and methodologies involved. Although there exist numerous reviews on catalysts for nitrate reduction, only a limited number have specifically synthesized the

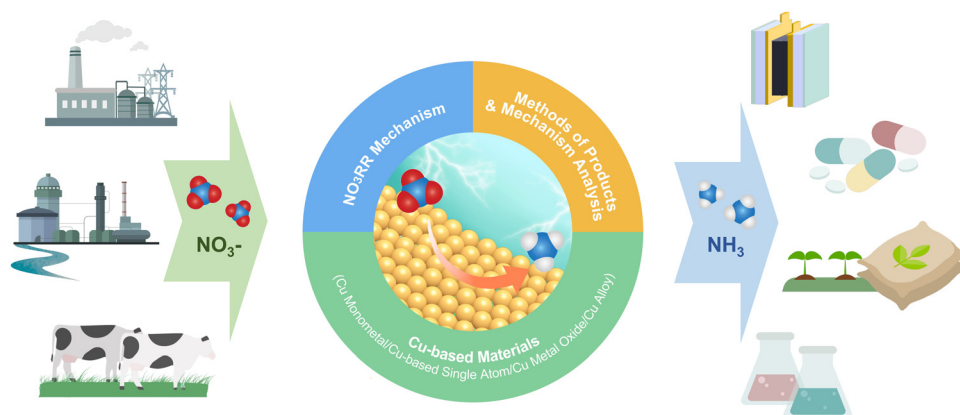


Fig. 1 Schematic illustration of the nitrate reduction reaction towards ammonia synthesis.



mechanisms and corresponding evaluation methods for a distinct material type. Given the exponential growth in research outputs in this field, there is a pressing need for a comprehensive, up-to-date review that encapsulates recent advancements. This review aims to fill this gap, providing a valuable resource that offers insightful guidance for ongoing research in this field of study. The main structure of this review is illustrated below (Fig. 1).

First, the reaction mechanism of NO₃RR is discussed from the perspectives of reaction pathways and intermediates, activity criteria, and selectivity criteria on Cu-based electrocatalysts. In addition, the main challenges of nitrate reduction for ammonia production would be clarified. Second, different types of Cu-based materials for electrocatalytic ammonia production are introduced. Third, the analysis methods for electrocatalytic ammonia production used in product (ammonia) detection, the characterization of reactive intermediates and active species on the electrode surface are introduced. Finally, the application of Cu-based catalysts in electrocatalytic ammonia production *via* NO₃RR and corresponding economic analysis are presented. The remaining challenges in the future development of NO₃RR will be highlighted and future perspectives will be proposed.

2. Insights into the electrocatalytic mechanism

The development of efficient catalysts with excellent activity and selectivity is highly dependent on the in-depth understanding of the electrocatalytic mechanism. In this section, the reaction mechanism of NO₃RR, including reaction pathways and intermediates, activity, and selectivity criteria, especially for Cu-based materials, will be described in detail as practical guidance for electrocatalyst design and selection.

Before delving into the reaction pathways and intermediates of NO₃RR, a general discussion of the working mechanism of NO₃RR is presented on an electrode scale as shown in Fig. 2. First, the nitrate ions (NO₃[−]) in the electrolyte migrate to the surface of the electrode, where they form adsorbed nitrate (*NO₃[−]). Then, the *NO₃[−] ion combines with water molecules and electrons and the NO₃RR takes place at the liquid–solid interface, converting *NO₃[−] into adsorbed ammonia (*NH₃). The electrons, in this case, are provided by the external circuit and transferred through the electrode. After that, *NH₃ desorbs from the surface, realizing the conversion from nitrate to ammonia. Generally, the NO₃RR involves a series of deoxygenation steps from nitrate to *NO (or *N), followed by hydrogenation steps to produce ammonia. In each elementary step, hydrogen transfer occurs between hydrogen donors (*H) and acceptors (adsorbate).³² The kinetics of the NO₃RR are strongly influenced by the nature of hydrogen transfer and the density of available hydrogen donors. However, if the *H recombine to form H₂ through the HER pathway, it reduces the availability of *H for the subsequent steps of NO₃RR and can limit the overall efficiency of ammonia production.

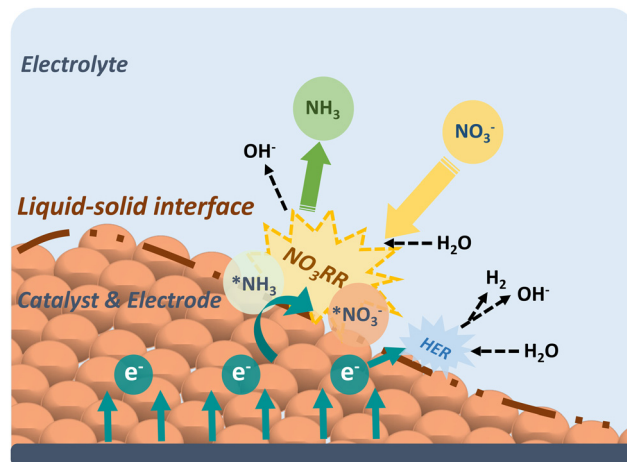


Fig. 2 The schematic illustrating the NO₃RR principle on an electrode-scale.

Therefore, studying the mechanism of NO₃RR is of utmost importance as it provides insights into the reaction pathway and enables the identification of strategies for regulating the process and minimizing the competing HER. A comprehensive understanding of the elementary steps involved in NO₃RR, including the deoxygenation and hydrogenation steps, allows researchers to pinpoint the critical factors that influence the reaction kinetics and selectivity. This knowledge can then be utilized to design catalysts with tailored properties or modify reaction conditions to optimize the NO₃RR process and mitigate the occurrence of the HER.

2.1. Reaction pathways and intermediates

With a broad span of valence states from NO₃[−] to NH₃ (ranging from +5 to −3), the conversion of nitrogen undergoes the complicated eight-electron transfer process involving a series of intermediates. In the whole process, intermediates such as NO₂[−]_{ads}, NO_{ads}, N₂O_{ads}, NH_{ads}, NH_{2ads}, NH_{2OHads}, *etc.* are involved between nitrate and ammonia. To better understand the mechanism, the reaction pathways and the intermediates of NO₃RR should be identified under a thermodynamics framework.³³ The overall reaction process of nitrate reduction towards ammonia could be presented in the form of an equation as shown below:³⁴




Wang *et al.* summarized that two parts compose the pathways of NO₃RR,³⁵ named the direct electrocatalytic reduction and indirect autocatalytic reduction pathways.^{36–38} In direct electrocatalytic reduction, nitrate participates directly in the electron-transfer process while the reaction pathways without nitrate participating in electron transfer are named indirect reduction pathways. The occurrence of either of the two pathways is highly dependent on the concentration of nitrate and protons. Typically, when the nitrate concentration is in the range of 1.0 M to 4.0 M and under highly acidic conditions, the




adsorbed NO_2^- would be protonated into nitrous acid (HNO_2), inducing two autocatalytic mechanisms which are known as the Vetter pathway and Schmid pathway.^{39–41} The products of these pathways include nitrogen oxide (NO), nitrogen dioxide (NO_2), nitrogen dioxide dimer (N_2O_4), and nitrous acid (HNO_2).⁴² Thus, indirect autocatalytic reduction pathways are unwanted when aiming for ammonia production.

The mechanism in direct electrocatalytic reduction pathways is categorized into two parts based on the different mediation of the reaction, namely, adsorbed hydrogen reduction and electron reduction. For the adsorbed hydrogen reduction pathway, the reaction is regulated by the adsorbed hydrogen atoms ($^*\text{H}$) which are formed through the reduction of H_2O (Volmer process) on the cathode surface.⁴³ Then, the $^*\text{H}$ functions to reduce the NO_3^- ions to NH_3 through a series of tandem reactions which are shown in the following equations proposed by Xu *et al.* (eqn (2.2)–(2.9)):⁴⁴



The electron reduction pathway, where electrons mediate the whole nitrate reduction reaction, is widely accepted. In this pathway, the nitrate is first catalyzed to nitrite by electrons and this reaction directly occurs on the surface of the electrode as shown in the equations below (eqn (2.10) and (2.11)).⁴⁴



However, for the process from nitrite to ammonia, different researchers have different opinions on the specific intermediates and pathways. In general, three typical pathways of NO_3RR to ammonia have been proposed on the surface of Cu catalysts^{33,45} (abbreviated as NRA). The method NRA1 as shown in Fig. 2 involves the formation of ammonia through the intermediate $^*\text{N}$, which is in accordance with the above equations proposed by Xu *et al.*^{46–48} In this pathway, it is worth mentioning that two $^*\text{N}$ might combine to produce N_2 as shown in eqn (2.12):⁷



However, the migration barrier of $^*\text{N}$ (0.75 eV) is much higher than the migration barrier of $^*\text{H}$ (0.10 eV). Besides, Gao *et al.* reported that the formation of N–H bonds is more favourable than that of N–N bonds in a kinetic perspective,⁴⁹ indicating a strong tendency towards ammonia rather than nitrogen (Fig. 3).



Fig. 3 The proposed direct electrocatalytic reduction pathways for nitrate reduction towards ammonia.

Another common pathway, named NRA2 and shown in Fig. 2, involves the intermediate $^*\text{NOH}$ throughout the whole reaction.^{24,50,51} There are similar deoxygenation steps in these two pathways until the formation of NO^* , and the main difference between these two pathways is the reaction sequence of hydrogenation and deoxygenation. Although these two pathways have been widely reported and reviewed, Hu *et al.* defined a more favourable pathway where deoxygenation happens on $^*\text{NHOH}$, forming $^*\text{NH}$.³³ This pathway is named NRA3. In Hu's work, all three pathways were evaluated on the commonly and stably exposed Cu (111) surface through density functional theory calculations under the defined condition of $\text{pH} = 0$. Gibbs free energies are regarded as a crucial factor in determining the spontaneity of a reaction and the key references in determining the reaction pathways. The results indicated that although NRA1 is more favourable in terms of thermodynamics, it exhibits sluggish kinetics with a higher energy barrier caused by the high activation energy (1.62 eV) of $^*\text{NO} \rightarrow ^*\text{N}$, which is 20 times higher than the activation energy (0.08 eV) of $^*\text{NO} \rightarrow ^*\text{NOH}$. Moreover, the activation energy (1.36 eV) of $^*\text{NHOH} \rightarrow ^*\text{NH}_2\text{OH}$ in NRA2 is much higher than the activation energy (0.23 eV) of $^*\text{NHOH} \rightarrow ^*\text{NH}$ in NRA3. Besides, the intermediates in NRA2 tend to desorb more easily (such as hydroxylamine), thus forming more byproducts and causing side effects on the selectivity. Moreover, free Gibbs energies of each pathway under $\text{pH} = 7$ and 14 are considered as well. Taking all these factors into account, NRA3 was proved to be the most probable pathway in NO_3RR over all pH ranges. Recently, Karamad *et al.* reported a pathway on Cu (111) similar to that in Hu's work,²⁶ named NRA4 in this review. However, there are two intermediates different from those in the former NRA3 pathway as shown in Fig. 2. Particularly, the intermediates involved in deoxygenation from $^*\text{NOH}$ to $^*\text{NH}$ differ between the two pathways, where $^*\text{N}$ is formed due to the reduction of $^*\text{NO}$. Despite the slight differences in pathways, the potential limiting step remains the hydrogenation from $^*\text{NO}$ to $^*\text{NOH}$.

Based on the NRA3 pathway, which is regarded as the most favourable pathway, the pH effects on the Gibbs free energies of the most typical Cu (111) surface are evaluated.³³ As shown in



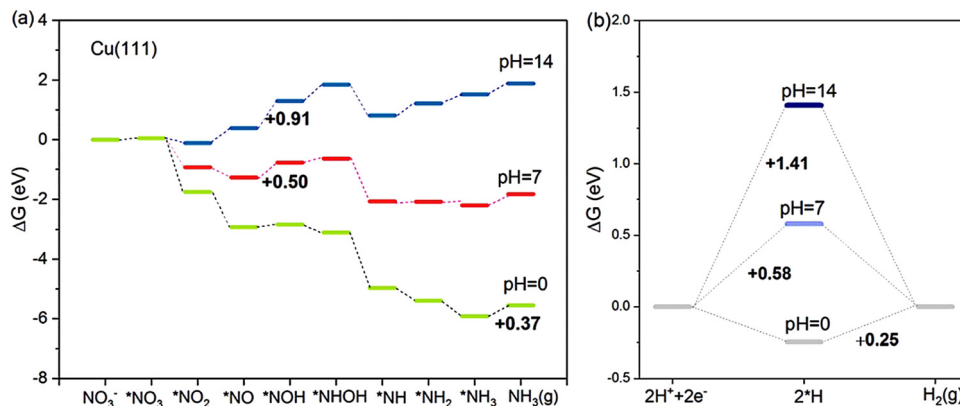


Fig. 4 The competition between (a) NO₃RR and (b) HER on Cu (111) at pH = 0, 7 and 14, studied by Hu *et al.* Reprinted with permission from ref. 33. Copyright 2021, American Chemical Society.

Fig. 4, at pH = 0, the rate-determining step is the desorption of *NH₃, which needs 0.37 eV in NRA3. However, under neutral conditions of pH = 7, the rate-determining step becomes the hydrogenation process *NO → *NOH with a free energy barrier of 0.50 eV. At pH = 14, the rate-determining step still occurs during this hydrogenation process with a higher Gibbs free energy of 0.91 eV. Speculated from the calculation results, the NO₃RR process is more energetically favourable at higher H⁺ concentrations (lower pH values). Meanwhile, the competition between the NO₃RR and HER is considered as well under the above three pH conditions. Under acidic conditions, the rate-determining step of HER is the formation of H₂ ($\Delta G_{\text{RDS}} = 0.25$ eV), of which the Gibbs energy is lower than that in NO₃RR, suggesting the inferior NO₃RR performance due to the strong HER. Under neutral and alkaline conditions, the cases are different: the rate-determining step of the HER is H⁺ → *H, with Gibbs free energies of 0.58 eV and 1.14 eV, respectively. Both these values are higher than the corresponding ΔG_{RDS} of the NO₃RR process, indicating the improved selectivity towards ammonia with suppressed HER. To sum up, at a higher concentration of H⁺, the energy barriers would be lower for both NO₃RR and HER. However, it is important to consider the competitive relationship between these two reactions when determining the optimal pH value for the NO₃RR and thus the selectivity for ammonia synthesis can be maximized.

2.2. Activity criteria

Activity is of primary importance in judging a specific catalyst and serves as a valuable guideline for developing a new catalyst. In general, for a particular catalyst, the catalytic activity for a reaction is decided by the applied potential and the adsorption strength of intermediates, affecting the concentration of both reactants and intermediates.⁴⁹ In the NO₃RR, the adsorption energies of the nitrogen atom and oxygen atom have direct impacts on the activities while the relationship between the maximum activity and the adsorption energies of a specific material is also controlled by the applied potential.

Liu *et al.* investigated the activities of different transition metals (Cu, Co, Rh, Pd, Ag, and Pt) at different applied

potentials (−0.2 V, 0 V, 0.2 V, and 0.4 V vs. reversible hydrogen electrode (RHE)) through computational mean-field microkinetic modelling based on density-functional theory (DFT).^{52–55} As shown in Fig. 4, the theoretical volcano plot of turnover frequencies (TOF) is constructed as a function of atomic oxygen and nitrogen adsorption energies. Comparing the maximum activities based on theoretical simulations, Cu has the highest activity in NO₃RR among non-noble metal catalysts, which is in accordance with the former report based on experiments.²⁹ Calculation of limiting potential steps is another approach for estimating the catalytic activities of metal.²⁶ As reported by Karamad *et al.*, the limiting potential step for Cu is *NO→*NOH with the corresponding limiting potentials of −0.23 V vs. RHE. Through comparison, it can be demonstrated that Cu is the most active among non-noble metal catalysts for NO₃RR.

2.3. Selectivity criteria

Selectivity is another principal factor that should not be neglected in designing efficient electrocatalysts. As a reaction with complicated reaction pathways, various byproducts can be generated during the NO₃RR process such as N₂, N₂O, NO, *etc.*³⁵ Similarly, both the adsorption energies (ΔE_{O} and ΔE_{N}) and the applied potential have great impacts on the selectivity towards products.⁵² As shown in Fig. 5, generally, with more negative potentials, NH₃ production would be promoted, whereas more positive potentials would promote selectivity towards N₂, which is in accordance with the higher standard electrode potential ($E^0 = 1.25$ V vs. RHE) in N₂ production. Meanwhile, the formation of N₂ requires strong adsorption energies for both atomic N and O while the formation of NH₃ prefers relatively moderate ΔE_{O} and ΔE_{N} . Consequently, Cu has the best selectivity towards ammonia in the NO₃RR among non-noble metals (Fig. 6).

Apart from the formation of byproducts, the hydrogen reduction reaction (HER) is a strong competitive reaction against NO₃RR under negative potentials. In this regard, the evaluation of NO₃RR selectivity over HER is a key evaluation criterion. It has been reported that the binding energy of *H is a reasonable descriptor for the activity of HER.^{56,57} To clarify the





Fig. 5 Theoretical volcano plots of the TOF as a function of atomic oxygen (ΔE_{O}) and nitrogen (ΔE_{N}) adsorption energies for electrocatalytic nitrate reduction on transition metal surfaces based on DFT-based microkinetic simulations at (a) -0.2 V, (b) 0 V, (c) 0.2 V, and (d) 0.4 V vs. RHE by Liu *et al.* Reprinted with permission from ref. 52. Copyright 2019, American Chemical Society.



Fig. 6 Theoretical selectivity maps to NO, N₂O, N₂, or NH₃ products from electrocatalytic nitrate reduction as a function of oxygen and nitrogen adsorption energy at (a) -0.2 V, (b) 0 V, (c) 0.2 V, and (d) 0.4 V vs. RHE by Liu *et al.* Reprinted with permission from ref. 52. Copyright 2019, American Chemical Society.

selectivity tendency towards HER or NO₃RR, Karamad *et al.* studied the relationship between the limiting potentials for HER and NO₃RR on various transition metals.⁵⁸ As shown in Fig. 7, $U_{\text{L}}(\text{NO}_3\text{RR}) - U_{\text{L}}(\text{H}_2)$ represents the selectivity tendency for NO₃RR over HER, while $U_{\text{L}}(\text{NO}_3\text{RR})$ reflects the activity tendency of NO₃RR. The most effective catalysts appear in the upper right corner of the figure. In conclusion, Cu is suggested to be the most active and selective transition metal catalyst for NO₃RR, making Cu-based materials promising for nitrate reduction towards ammonia.



Fig. 7 The differences between the limiting potentials for the NO₃RR and HER by Xu *et al.* Reprinted with permission from ref. 26. Copyright Royal Society of Chemistry.

In conclusion, with the great interest in Cu-based electrocatalysts for NO₃RR, many works investigating the mechanism insights into Cu-catalyzed-NO₃RR have been reported through theoretical calculations. Various pathways of NO₃RR have been proposed with no definitive conclusion although the previously discussed NRA3 route is regarded more favorable on Cu. Besides, the activity and selectivity of Cu-based materials have been proven from the perspective of the underlying mechanism.

3. Cu-based materials

NO₃RR is a promising electrocatalytic reaction of ammonia production. However, the complex electronic pathways of NO₃RR to ammonia require highly active and selective electrocatalysts to counteract other competing reactions, of which HER is the most prominent. During the last few decades, various electrocatalysts have been reported to have excellent performance in the electrochemical synthesis of ammonia.^{59–61} Among them, transition metal-based catalysts, which have the unique electronic structure of partially filled d-orbitals, can easily donate and accept electrons from other molecules, therefore achieving the strong absorption of electron-rich nitrogen atoms.⁶² Meanwhile, the transition metal-based catalysts have the potential to inhibit the competing HER and raise the energy barriers for the by-products, thus promoting the FE of NO₃RR and the selectivity towards ammonia.⁴⁵ Besides, it has been demonstrated that the electron transfer can be accelerated due to the close energy levels between the highly occupied d-orbitals (HOMOs) and the lowest empty π -orbitals (LOMOs) of the transition metal-based catalysts.²⁴ Following these considerations, transition metal-based electrocatalysts have been extensively studied and reported as promising catalysts for electrochemical ammonia synthesis.^{20,63,64}

The first reported Cu electrocatalyst for nitrate reduction was developed in 1979 by Pletcher and Poorabedi.⁶⁵ In this work, the Cu disc working electrode acted as a catalyst in acidic perchlorate and sulfate as media, confirming the feasibility of



nitrate reduction to ammonia through the electrochemical pathway. However, in the next several decades, only a limited number of works were reported because of the low FE and ammonia yield, which made this method of ammonia production seem worthless compared to biological and industrial methods.^{19,66–68} It was not until recent years that the field of electrochemical ammonia synthesis attracted the interest of researchers again due to the increasing demand for green ammonia with the aim of carbon neutrality. Besides, along with the outstanding advances in nanomaterial synthesis and characterization methods, many newly designed electrocatalysts have been reported since then.

To date, a large number of noble metal catalysts such as Ru, Rh, Pt, Pd, Au, *etc.* as well as their bimetallic and other novel structures/morphologies have been extensively investigated, showing satisfactory performance, including low overpotential which means limited energy consumption, high FE and ammonia yield rate.^{69–77} However, the high cost and low reserves of noble metals limit their potential for large-scale industrial applications. As a result, the non-noble transition metal catalysts, which not only have relatively low cost and abundant sources but also demonstrate comparable activity for the electrochemical synthesis of ammonia, have attracted considerable interest from researchers.^{78–81}

Among these noble metal-free catalysts, Cu and Cu-based materials are promising candidates for NO₃RR and even show better selectivity and activity than many noble metal catalysts, which has been proven through the comprehensive evaluation of both experimental results and computational theoretical analysis.²⁶ To achieve ideal product selectivity and reaction kinetics, there has been a tremendous interest in developing advanced Cu-based electrocatalysts for NO₃RR *via* tuning the Cu active site through various strategies such as crystal facet engineering, electronic and geometric tuning, alloying and doping modifications, single atom dispersion strategies.^{82–84} In addition, the design of copper-based catalysts involves careful selection and engineering of support materials to enhance their catalytic performance. This comprises the use of specific

support materials with specific surface properties, porosity and electronic interactions with copper species.

In this section, the Cu-based materials functioning as electrocatalysts in the nitrate reduction reaction for ammonia production will be catalogued and introduced individually. The table below summarizes the state-of-the-art electrochemical performances of Cu-based materials in the NO₃RR (Table 1).

3.1. Cu monometal

As early as 1979, a Cu disc was used as the cathode in aqueous acidic perchlorate and sulphate media for the first time.⁶⁵ The experiments revealed that nitrate ions could be eventually reduced to ammonia if sufficient protons were provided in the reaction. The authors also proposed that the nitrate reduction is sensitive to the reaction condition, especially the electrode materials. Although the experimental and characterization methods were relatively poor compared to the present technology, this work did provide significant inspiration for further research on copper-based electrocatalysts at that time.

Owing to the rapid development of nanotechnology, even monometallic materials have given rise to numerous fine-structure catalysts. When Cu is minimized down to the nanometer scale in one or several directions, the motion of electrons in this direction is subjected to confinement, which triggers a transition in the properties of the material and has a profound effect on the catalytic performance.⁹⁶ For example, Fu *et al.* reported a Cu nanosheet catalyst for nitrate reduction to ammonia with extremely high ammonia selectivity.⁸² The FE reached a record-high value of 99.7% FE at -0.15 V vs. RHE, with an ammonia yield rate of $390.1 \mu\text{g mg}_{\text{Cu}}^{-1} \text{h}^{-1}$, which was over 400 times higher than that of bulk Cu foil. The outstanding performance could be attributed to the suppressed HER and increase in the current density of the rate-determining step, namely, nitrite generation (S_1) in this reaction. It is worth mentioning that the authors analyzed the reduction peaks exhibited on the LSV curves corresponding to four different reaction processes (S_1 , S_2 , S_3 , and S_4) as shown in Fig. 8.^{82,97,98}

Table 1 The electrochemical performances of Cu-based materials in the NO₃RR

| Material-type | Name | Potential | FE (%) | Yield | Electrolyte | Ref. |
|----------------|-------------------------------------|--|--------|---|---|------|
| Cu monometal | Cu disc | -0.55 V vs. SCE | 68 | N/A | 1.0 M HClO ₄ and 5 mM NO ₃ [−] | 65 |
| | Cu nanosheet | -0.15 V vs. RHE | 99.7 | $0.39 \text{ mg mg}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 0.1 M KOH and 10 mM KNO ₃ | 82 |
| | Cu nanodisk | -0.5 V vs. RHE | 81.1 | $2.16 \text{ mg mg}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 0.1 M KOH and 10 mM KNO ₃ | 85 |
| Cu single atom | Cu(I)-N ₃ C ₁ | -0.64 V vs. RHE | 65.3 | $76.52 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 50 mM Na ₂ SO ₄ and 7.1 mM NaNO ₃ | 86 |
| | Cu-N-C SAC | -1.0 V vs. RHE | 84.7 | $212.5 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 0.1 M KOH and 0.1 M KNO ₃ | 87 |
| | Cu-N-C | -1.5 V vs. SCE | 94 | $9.23 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 0.5 M Na ₂ SO ₄ and 3.6 mM NaNO ₃ | 88 |
| | Cu@Cu ₂₊₁ O NWs | -1.2 V vs. SCE | 78.57 | $0.58 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 1.0 M K ₂ SO ₄ and 7.1 mM KNO ₃ | 48 |
| Cu oxide | Cu ₂ O | -0.8 V vs. RHE | 92.28 | N/A | 0.5 M Na ₂ SO ₄ and 5.0 mM NaNO ₃ | 89 |
| | Cu ₂ O (100) facets | -0.6 V vs. RHE | 82.3 | $0.74 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 0.1 M Na ₂ SO ₄ and 3.6 mM NaNO ₃ | 90 |
| | Cu ₂ O-OV | -1.1 V vs. Ag/AgCl | 89.54 | $1.40 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 0.5 M Na ₂ SO ₄ and 3.2 mM NO ₃ [−] | 91 |
| | Ru-Cu NW | -0.13 V vs. RHE (1 A cm ^{−2}) | 90 | $76.5 \text{ mg cm}^{-2} \text{h}^{-1}$ | 1.0 M K ₂ SO ₄ and 32.3 mM KNO ₃ | 77 |
| Cu alloy | CuCo nanosheets | -0.2 V vs. RHE (1035 mA cm ^{−2}) | 100 | $0.96 \text{ mg g}_{\text{Cu}}^{-1} \text{h}^{-1}$ | 1.0 M KOH and 100 mM KNO ₃ | 92 |
| | Au ₁ Cu (111) | -0.2 V vs. RHE | 97 | $0.55 \text{ mg cm}^{-2} \text{h}^{-1}$ | 0.1 M KOH and 7.1 mM KNO ₃ | 93 |
| | Cu ₄₉ Fe ₁ | -0.7 V vs. RHE | 94.5 | $3.91 \text{ mg cm}^{-2} \text{h}^{-1}$ | 0.1 M K ₂ SO ₄ and 3.2 mM KNO ₃ | 94 |
| | Cu ₅₀ Ni ₅₀ | -0.15 V vs. RHE | 99 | N/A | 1.0 M KOH and 0.1 M KNO ₃ | 74 |
| | Rh@Cu | -0.2 V vs. RHE | 93 | $21.59 \text{ mg cm}^{-2} \text{h}^{-1}$ | 0.1 M Na ₂ SO ₄ and 0.1 M NaNO ₃ | 83 |
| | 10Cu/TiO _{2-x} | -0.75 V vs. RHE | 81.34 | $1.94 \text{ mg cm}^{-2} \text{h}^{-1}$ | 0.5 M Na ₂ SO ₄ and 3.2 mM NaNO ₃ | 95 |





Fig. 8 Electroreduction of nitrate to ammonia on the copper catalyst. (a) Linear sweep voltammetry curves of copper catalysts on carbon paper measured in 0.1 M KOH (dotted line) in the presence of 10 mM KNO₃ (solid line). Scan rate: 20 mV s⁻¹. (b) Current densities, (c) ammonia yield rates and (d) Faradaic efficiencies of various Cu catalysts for ammonia production at different applied potentials. Preprinted with permission from ref. 76. Copyright 2020 Elsevier Ltd.

The equations/processes of the reactions are given below (eqn (3.1)–(3.3)):



S₄: competing adsorption (H_{ad}) of the intermediate N-species

Modulating the crystalline surface of catalysts is an efficient strategy for optimizing the intrinsic catalytic properties. The facile synthesis of uniform Cu nanodisks with exposed Cu (111) facets, serving as a highly active ammonia-producing catalyst, was reported by Wu *et al.*⁸⁵ Using oxidative oxygen gas and reductive glucose, the Cu nanodisks, measuring only 7 nm in thickness and 80 nm in diameter, were synthesized through a three-day reaction. Although the surface of Cu nanodisks was partly oxidized, the majority of the catalysts remained in metallic states. During the process of nitrate reduction, the partly oxidized surface was also deoxidized, reconstructing the Cu (111) face. In this work, 0.1 M KOH, 0.1 M KOH with 10 mM KNO₃ and 0.1 M KOH with 10 mM KNO₂ were chosen as comparisons, respectively. It was found

that Cu nanodisks exhibit better adsorption of nitrate than nitrite from the overpotential of LSV curves. The selectivity of NO₃RR to ammonia reached its peak with a maximum FE of 81.1% at -0.5 V vs. RHE and a maximum ammonia yield rate of 2.16 mg mg_{cat.}⁻¹ h⁻¹ at -0.63 V vs. RHE, respectively.

It was noteworthy that the ammonia yield rate was confirmed using both ¹H nuclear magnetic resonance (NMR) spectra and the regular indophenol-blue method through ultraviolet-visible (UV-vis) spectroscopy, improving the data reliability.¹⁶ The details of the methods will be introduced in later sections. Since Cu (111) was reconstructed from the oxidation state of copper, the perfect Cu (111) surface was compared with the reconstructed Cu (111) surface in the investigation of catalytic mechanisms through DFT calculations. It could be concluded that the surface triatomic Cu clusters formed in the reconstruction weakened the interaction of N–O bonds and exhibited better absorption of NO₃⁻, hence improving the NO₃RR performance to a practical standard. Besides, when the size of Cu is minimized, it can be reduced to the ultimate form of nanoparticles – Cu single atoms, which exhibit unique electronic structures that maximize atomic utilization.⁹⁹ The specific discussion on this type of electrocatalyst will be addressed in a later section.



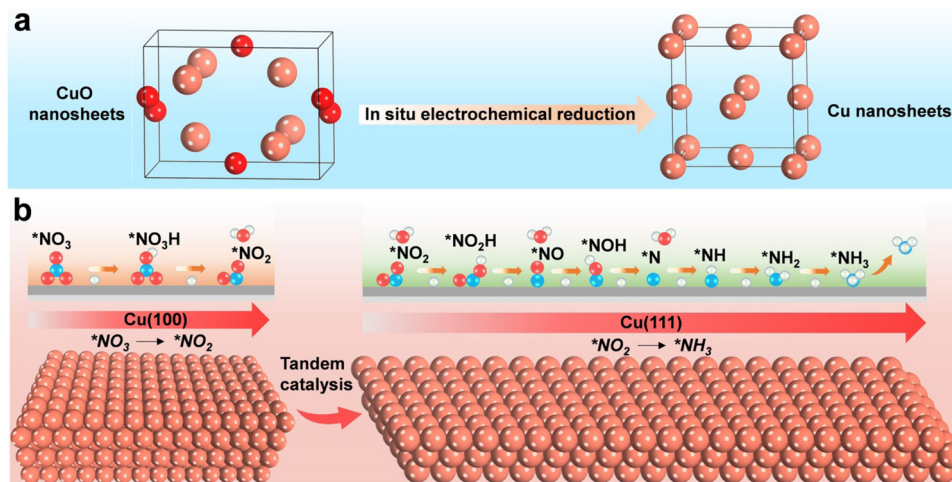


Fig. 9 Schematic illustration for enhancing the electrochemical NO_3RR over Cu nanosheets via tandem catalysis. (a) Electrochemical *in situ* reduction of the as-prepared CuO nanosheets during NO_3RR . (b) Tandem interaction of Cu (100) and Cu (111) facets. Reprinted with permission from ref. 100. Copyright 2023 Wiley-VCH Verlag GmbH.

Furthermore, recent studies have also explored facet tandem catalysis using Cu monometal catalysts. By modifying the Cu (100) and Cu (111) facets, a tandem catalysis system is created (Fig. 9), where nitrite is generated on the Cu (100) facet and subsequently hydrogenated on the Cu (111) facet.¹⁰⁰ This tandem catalysis mechanism is achieved through crystal face engineering and has demonstrated high-performance NO_3RR with an ammonia yield rate of $1.41 \text{ mmol h}^{-1} \text{ cm}^{-2}$ at -0.59 V vs. RHE, and excellent stability over 700 hours.

3.2. Cu single atoms

Although bulk Cu metallic catalysts have been widely investigated in the nitrate reduction reaction for ammonia production, it still suffers from low stability and activity, especially after long-term operation.^{50,97} According to previous research, there are two issues related to this unsatisfactory performance, which are catalyst deactivation caused by corrosion and nitrite poisoning.⁶¹ To overcome these limitations, minimizing the size of Cu nanoparticles to a single-atom level is a promising strategy for Cu-based catalysis of NO_3RR . Single-atom catalysts offer prominent advantages in terms of extremely high utilization efficiency and unique catalytic performance compared to their bulk materials.^{100–102} Specifically, several highlights attributing to these advantages are listed below: (1) adequately exposed active sites facilitate strong adhesion and conversion of the reactants, leading to better activity; (2) homogeneous active sites and structures allow uniform interaction between active sites and substrates, leading to better selectivity; and (3) the strong interactions between single atoms and coordination atoms stabilize the single metal atoms, leading to a better stability.^{103,104} Thus, using single atoms as catalysts has been a new frontier in the electrochemical catalysis area and several works have reported Cu single-atom catalysts for ammonia production through NO_3RR .^{87,88,105}

For instance, Zhu *et al.* reported a metal–nitrogen–carbon (M–N–C) catalyst with Cu single atoms embedded into the

nitrogenated carbon nanosheet (Cu–N–C), exhibiting extraordinary activity, selectivity, and stability in nitrate reduction reaction.^{104,105} The Cu–N–C single-atom catalyst was synthesized through pyrolysis of Cu–MOFs as a precursor in an Ar atmosphere. Also, the effect of annealing temperature on the size of Cu nanoparticles/atoms on the nanosheet was studied, revealing that increasing temperature resulted in the aggregation of Cu atoms. It is worth mentioning that when the annealing temperature was lower than $800 \text{ }^\circ\text{C}$, the Cu atoms were not exposed, but covered with a thick layer of carbon. The formation of Cu single atoms at $800 \text{ }^\circ\text{C}$ was confirmed through high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) images, XRD, X-ray absorption near edge structure (XANES) and extended X-ray absorption fine structure (EXAFS). In this catalyst, Cu existed in the form of Cu(I) and Cu(II) due to the formation of Cu–N₄ and Cu–N₂. Cu(0) was not observed until the formation of Cu nanoparticles, as shown in Fig. 8. As a critical factor for electrocatalyst development, the outstanding stability of the Cu–N–C single-atom catalyst was clarified. Compared to Cu–N–C nanoparticles (pyrolysis temperature of $900 \text{ }^\circ\text{C}/1000 \text{ }^\circ\text{C}$), it maintained a superior electrocatalytic performance with only 5.4% declination after 20 consecutive cycles. Moreover, through both experimental methods and theoretical calculations, the Cu–N–C single atom catalyst was proved to alleviate the nitrite production and accumulation compared to other bulk Cu catalysts, addressing a critical issue of Cu-based catalysts in NO_3RR .

Yang *et al.* also reported Cu–N–C SAC for nitrate reduction to ammonia with a high Faradaic efficiency of 84.7% at -1.00 V (vs. RHE) and an ammonia yield rate of $4.5 \text{ mg cm}^{-2} \text{ h}^{-1}$.⁸⁷ The synthesized catalyst featured a mesoporous structure and a large specific area of $1065 \text{ m}^2 \text{ g}^{-1}$. In Cu–N–C SAC, the concentration of Cu was determined to be 1.0 wt%, and the content of N was 10.23 at%. The authors also revealed another mechanism of Cu–N–C, in which the Cu single atoms would reconstruct into nanoparticles during the electrochemical



reduction process. The valence state of fresh Cu–N–C SAC was Cu(I) in the form of Cu–N₄. However, in the nitrate reduction reaction process, Cu(I) was also reduced and aggregated into metallic Cu, which could be figured out in HAADF-STEM images. After the electrolysis, the aggregation of Cu⁰ nanoparticles would disintegrate reversibly and be stored in the Cu–N₄ structure again after reoxidation in air. Besides, operando XAS and density functional theory calculations were also applied in the study to unveil the dynamic evolution of the Cu–N_x structure.

Most recently, Li *et al.* systematically unveiled the size effect of the Cu-based catalyst in NO₃RR.⁹⁹ Aiming at the study of size effects, the authors tailored the Cu-based catalyst ranging from single-atom catalysts to single-cluster catalysts and nanoparticles. The study revealed the effect of size and the coordination environment on the high catalytic activity and selectivity for the NO₃RR and suggested a promising design strategy for size-controlled aerogel-based catalysts for various electrocatalytic reactions.

3.3. Cu metal oxide

Metal oxides are another major class of metal catalysts with various surface morphologies and compositions. Transition metal oxides occupy an important position in the catalysis field and contribute to relatively high catalytic activity. Among them, Cu metal oxides have been proven to be one of the most effective catalysts for electrochemical ammonia production.

Alongside the direct formation of Cu metal oxides during the synthesis process, copper-based materials may undergo phase changes during the electrocatalysis process, forming copper metal oxides with different surfaces and compositions, resulting in different catalytic properties. Thus, the real active sites in electrochemical reactions might not be the original species on the electrode surfaces and *in situ* characterization studies are required in research.

Commonly, Cu₂O is regarded as the real active sites for nitrate reduction to ammonia.^{89,90,106} Wang *et al.* unveiled the origin of the selectivity of nitrate reduction to ammonia on copper-based electrocatalysts.⁵⁰ The CuO nanowire arrays were synthesized and reported with an outstanding FE of 95.8% at –0.85 V in 0.5 M Na₂SO₄ with only 200 ppm N-nitrate. The synthesis procedure of this catalytically efficient copper-based nanowire array was very simple through *in situ* growth and thermal treatment on Cu(OH)₂ NWAs under an oxygen atmosphere at 300 °C. Through *in situ* electrochemical Raman spectra combined with XRD pattern and AES (Auger electron spectroscopy) spectra as shown in Fig. 10, the electrochemical reconstruction during the reaction process was confirmed. In this process, CuO NWAs were converted to Cu/Cu₂O NWAs through *in situ* reduction. The author proposed that the formation of Cu/Cu₂O promoted the electron transfer at the interface, which was further demonstrated in DFT calculations. The electrochemical method could also help illustrate the process; the CuO NWAs without pre-reduction showed an increased current density, which could be attributed to the reduction of CuO. Also, compared to bare Cu, extra electron

density could be observed through the theoretical model. The energy barrier of hydrogen evolution was also calculated. Cu/Cu₂O NWAs (0.33 eV) exhibited a much higher HER energy barrier than Cu NWs (0.12 eV), indicating an inhibiting effect and low activity towards HER. In conclusion, it was deduced that the high electron density led to a lower reaction barrier that inhibited the competitive HER, resulting in high conversion, FE and selectivity of Cu/Cu₂O in nitrate reduction for ammonia.^{105,107–109}

Qin *et al.* investigated the mechanism of nitrate reduction to ammonia on different exposed facets of copper oxides. Two exposed facets of Cu₂O, namely, Cu₂O (111) and Cu₂O (100), were investigated. The authors found that Cu₂O (100) achieved higher selectivity and activity compared to Cu₂O (111) due to the lower barrier energy. The variation in electronic properties was considered to be the reason for the difference and was investigated through theoretical calculations. Ren *et al.* fabricated a concave–convex surface Cu₂₊₁O layer on Cu nanowires.⁴⁸ In this electrode material, the interior metallic Cu improved the electronic transmission ability while the exterior Cu₂₊₁O layer provided more active sites for nitrate reduction on the electrode surfaces. Besides, the Cu/Cu₂₊₁O interface affected the modulation of the Cu d-band center, thus tuning the adsorption energies of various intermediates in the process. The highest ammonia-yielding FE of 87.07% was achieved under –1.2 V vs. saturated calomel electrode in a neutral solution.

Surface metal is usually considered as the active site in electrocatalytic reactions. Thus, anionic species including oxygen vacancies, hydroxyl groups, anion doping, *etc.* have been widely reported in recent works to be beneficial in promoting the activity of catalysts.^{110–114} For Cu oxide catalysts, creating oxygen vacancies using plasma treatment is an effective method for further improving the electrocatalytic NO₃RR to ammonia.⁹¹ The laser-irradiation technique is an effective strategy for creating oxygen vacancies.¹¹⁷ Geng *et al.* employed laser irradiation in fabricating oxygen vacancy-rich CuO_x nanoparticles which finally realized a large ammonia yield rate of 449.41 μg h^{–1} mg^{–1} with a FE of 74.18% at –0.25 V vs. RHE.¹¹⁸ Besides, Gong *et al.* reported the promotion of oxygen vacancies and hydroxyl groups on the surface of Cu₂O after plasma treatment, facilitating better adsorption of nitrate and proton transfer. This contributed to a strongly enhanced selectivity, leading to outstanding selectivity reaching 85.7% and FE reaching 89.54% towards ammonia. Further in depth, the impact of plasma treatment time was studied, with results indicating that the hydroxylation of material surface reached the peak at a treatment of 40 min while a further increase in treating time led to the loss of hydroxyl groups from the surface.^{115,116}

3.4. Cu-based alloy

Compared with single metal catalysts, alloy metal catalysts could modify the charge distribution on the catalyst through the introduction of other metals.⁴⁵ On the one hand, heterogeneity within and between particles gives rise to various active sites and particle morphologies.^{119,120} In the nitrate reduction



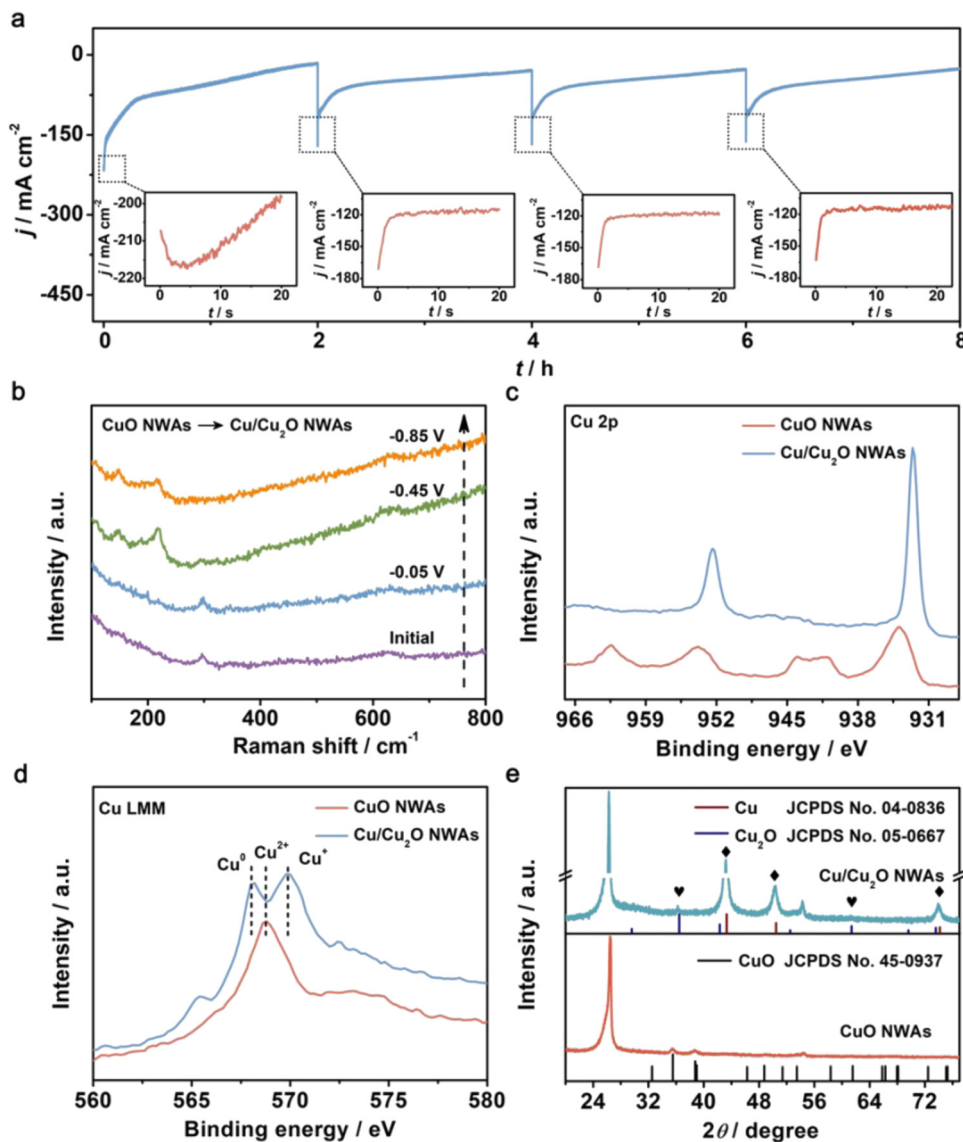


Fig. 10 (a) The i - t curves of CuO NWAs during four consecutive cycling NRA processes at -0.85 V. Insets: enlarged details in the dotted box. (b) *In situ* electrochemical Raman spectra of CuO NWAs under given potentials. (c) Cu 2p XPS spectra of CuO NWAs and Cu/Cu₂O NWAs. (d) Cu LMM AES spectra and (e) XRD patterns of CuO NWAs and Cu/Cu₂O NWAs. Reprinted with permission from ref. 50. Copyright 2020 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim.

reaction, additional metals can introduce their intrinsic properties, such as inhibition of nitrite production or formation of sequential reaction mechanisms, thus improving the electrochemical performance of the catalyst.^{74,79,84,121–123} On the other hand, some researchers believed that Cu-based alloys could enhance the resistance to corrosion significantly and improve the long-term stability compared with Cu monometal catalysts.^{94,121,122,124,125} Indeed, combining copper (Cu) with a metal of lower electronegativity can mitigate oxidation, reducing Cu²⁺ formation. This strategy enhances the corrosion resistance of the Cu-based alloy, as the secondary metal's electron-donating capacity decreases the likelihood of Cu oxidation. Additionally, forming heteroatomic Cu-M bonds with high dissociation energy further inhibits Cu dissolution. These strategies collaboratively enhance the corrosion resistance of

Cu-based alloys, significantly improving the long-term stability of Cu-based electrocatalysts, making them suitable for harsh environments and extended use.¹²⁶

Guo *et al.* reported metasequoia-like CuFe nanocrystals as a high-performance electrocatalyst for the NO₃RR.⁹⁴ The doping of Fe deepened the energy level of the Cu 3d band and favourably tuned the adsorption energy of the reaction intermediates, which led to improved activity with high FE and selectivity. Sargent *et al.* introduced Ni to form a CuNi alloy system in which the d-band center of Cu was tuned, and the adsorption energy of intermediates was modified. The positive shift of the d-band center was proved by combining the results of UPS and XPS. Also, the mechanism was further confirmed through DFT studies. Compared with pure Cu, the modified Cu₅₀Ni₅₀ alloy catalyst achieved a six-fold increase in NO₃RR



activity in the electrolyte comprising 1 M KOH and 100 mM KNO_3 . Gao *et al.* alloyed Cu with Ru and fabricated the reduced-graphene-oxide-supported RuCu alloy catalysts ($\text{Ru}_x\text{Cu}_x/\text{rGO}$) for direct NO_3RR .⁸⁴ The efficient activity of $\text{Ru}_x\text{Cu}_x/\text{rGO}$ can be attributed to the synergistic effect between Ru and Cu sites through relay catalysis, in which Cu exhibits efficient activity in the reduction of NO_3^- to NO_2^- , while Ru shows excellent activity in the reduction of NO_2^- to NH_3 . In addition, doping Ru with Cu can adjust the d-band centre of the alloy and effectively regulate the adsorption energies of NO_3^- to NO_2^- , thus promoting the ammonia production performance.

The CuCo alloy is one of the most widely reported types of electrocatalysts for NO_3RR .^{127–130} For this Cu–Co binary catalyst, He *et al.* also proposed a tandem catalysis mechanism.¹³¹ Specifically, Cu was the perfect active site for binding NO_3^- and catalyzing NO_3^- to NO_2^- while Co was highly selective towards the conversion of NO_2^- to NH_3 . Based on prior research, Fang *et al.* reported a CuCo bimetallic catalyst with excellent activity and selectivity for nitrate reduction to ammonia.⁹² At -0.2 V vs. RHE, the CuCo nanosheet delivered a FE of 100% under an industrial current density of 1035 mA cm^{-2} under alkaline condition (1 M KOH with 100 mM KNO_3), representing the world-record performance for NO_3RR so far. The addition of Co to Cu resulted in a fast electron transfer rate, as shown in electron transfer numbers and Tafel slopes (Fig. 11), providing electrons and hydrogen protons to nearby Cu species efficiently and enhancing the utilization of nitrate. *In situ* Fourier transformed infrared spectroscopy (FTIR) and *in situ* SHINERS associated with DFT calculations were applied to clarify the mechanism of the synergistic effect of Cu and Co.

Similarly, Fu *et al.* reported self-supported CoO/Cu foam as an efficient NO_3RR catalyst.¹³² Through the establishment of an electric field at the interface between Cu foam and CoO, the electron transfer from Cu to CoO is enhanced, resulting in the positive charge on Cu, which further enhances the adsorption of nitrate ions. This mechanism greatly improved the selectivity for ammonia, reaching a Faraday efficiency of 96.7% with the highest ammonia yield rate of 4.3 $\text{mg cm}^{-2} \text{h}^{-1}$, which is far beyond the performance of blank Cu foam and CoO on Ni foam. Recently, Liu *et al.* also reported core-shell heterostructure nanowire arrays ($\text{CuO NWAs}@ \text{Co}_3\text{O}_4$) for NO_3RR .¹³⁰ The copper-cobalt heterostructure is synthesized through a simple two-step method including *in situ* growth of $\text{Cu}(\text{OH})_2$ NWAs and the on-site growth of Co_3O_4 flocs. This resulted in a high ammonia yield rate of 1.915 $\text{mmol cm}^{-2} \text{h}^{-1}$ along with a Faraday efficiency of 99.17%. The authors attribute the enhanced activity to the synergistic effect of the active phases and improved atomic hydrogen adsorption. Based on the above views, although the specific mechanisms may vary between these works, they all shed light on the potential of utilizing Cu and Co in combination for enhanced catalytic performance.

Recently, there have been some works comparing different Cu-based alloys transversely from not only theoretical but also experimental perspectives. Zheng *et al.* studied a series of Cu-based diatomic site catalysts ($\text{CuTM}/\text{g-CN}$, TM = Fe, Co, Ni, Zn, Ti, V, Cr, and Mn) using theoretical insights.¹³³ Zhao *et al.* focused on the horizontal comparison between different Cu-based alloys (abbreviated as CuM), including CuCo, CuFe, and CuNi on the ordered mesoporous carbon (abbreviated as OMC).¹²⁴ The CuM/OMC series were synthesized through a

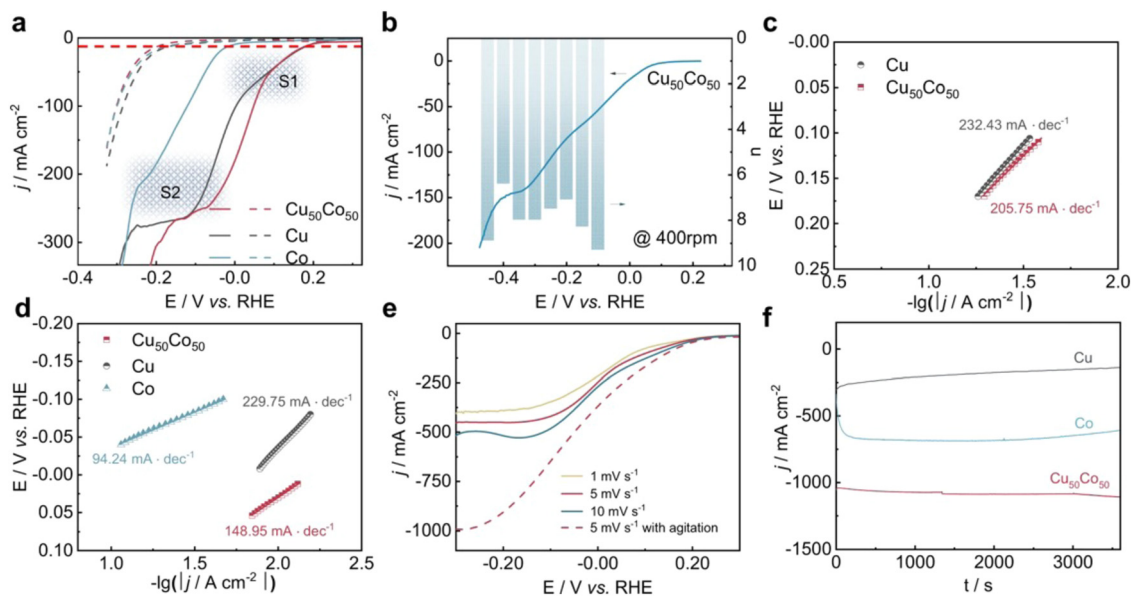


Fig. 11 Electrochemical performance of NO_3RR over $\text{Cu}_{50}\text{Co}_{50}$, pure Cu, and pure Co modified Ni foams reported by Fang *et al.* (a) j - E curve (80% i -R corrected) of the samples in a 1 M KOH solution containing 100 mM KNO_3 (solid lines) or in the absence of KNO_3 (dotted line) at a scan rate of 1 mV s^{-1} . (b) j - E curve (80% i -R corrected) at 400 rpm and electron transfer numbers at different potentials. (c) and (d) Tafel slopes in the potential range of peaks S1 and S2, respectively. (e) j - E curves over $\text{Cu}_{50}\text{Co}_{50}$ in a 1 M KOH solution containing 100 mM KNO_3 at different scan rates with/without agitation. (f) Time-dependent current density curves at -0.2 V with a magnetic stirring speed of 1000 rpm. Reprinted with permission from ref. 92 Copyright 2022 Springer Nature.



simple hydrothermal method assisted with the coprecipitation method and different ratios of metal were investigated. Among them, the optimal ammonia yield rate at -0.8 V vs. RHE follows the following order: $\text{Cu}_5\text{Fe}_5/\text{OMC} > \text{Cu}_5\text{Co}_5/\text{OMC} > \text{Cu}_7\text{Ni}_3/\text{OMC} > \text{Cu}/\text{OMC} > \text{Fe}/\text{OMC} > \text{Co}/\text{OMC} > \text{Ni}/\text{OMC} > \text{OMC}$. All the CuM catalysts showed superior ammonia yield rates compared with monometallic catalysts, experimentally proving the promotion of synergistic effects in NO_3RR .

To sum up, the four main types of Cu-based catalysts introduced above all show great potential in realizing high activity and selectivity in NO_3RR . Meanwhile, considering the outstanding advantages such as low cost and high electrical conductivity, Cu-based catalysts merit further investigation and hold promise for practical applications in ammonia production *via* NO_3RR . Several strategies are commonly employed for the development of Cu-based catalysts in NO_3RR . (1) Nanostructuring: reducing the size of Cu catalysts to the nanoscale can increase the surface area and expose more active sites, leading to improved catalytic activity. Cu nanoparticles, nanowires, or even Cu single atoms have shown promising performance in NO_3RR due to their unique electronic and structural properties. (2) Surface modification: introducing oxygen vacancies or nitrogen doping into the Cu-based catalyst surface can improve their electrocatalytic performance in NO_3RR . (3) Crystal facet engineering: controlling the crystal facets of Cu catalysts can significantly influence their catalytic activity. Optimizing the exposure of specific facets (*e.g.*, Cu (100) and Cu (111)) can enhance the overall catalytic performance. (4) Alloying with other metals: incorporating Cu with other metals, such as Co, Ag, Ru or Pd, can enhance the catalytic activity and selectivity of Cu-based catalysts through the synergistic effect.

4. Methods of product/mechanism analysis

To justify the performance of electrocatalytic synthesis of ammonia, three evaluation criteria should be adopted, which are activity, selectivity, and stability. Regarding the judgment of the electrode activity and stability, the electrochemical tests, such as cyclic voltammetry (CV), linear sweep voltammetry (LSV), chronoamperometry, electrochemical impedance spectroscopy (EIS) analysis, electrochemical surface area (ECSA), *etc.* are universal methods.¹²³ These tests are usually conducted and recorded through an electrochemical workstation. A three-electrode system is a common setup used in electrochemical experiments, particularly in H-cell configurations. It consists of two chambers separated by a membrane and three electrodes: a working electrode, a reference electrode, and a counter electrode. The three-electrode system in an H-cell configuration allows precise control and measurement of the electrochemical processes, making it a widely used setup in electrochemical research and applications. However, despite being essential indicators, electrochemical test results alone are insufficient to assess ammonia production performance. One major challenge is that the products of this reaction are

complex and diverse due to the wide valence distribution from +5 to -3 in NO_3RR . Simultaneously, the competing HER, which affects product selectivity, also contributes to a portion of the cathodic current. Besides, the electrochemical test results can only imply the occurrence of corresponding reactions in terms of the onset potential. Therefore, the products of NO_3RR and ammonia yield could not be analyzed precisely and quantitatively in this way.¹³⁴ Considering the evaluation of selectivity, product detection methods, especially for ammonia detection, are indispensable. As a critical metric for ammonia production, on one hand, Faraday efficiency (FE) describes the efficiency with which electrons are utilized in the system to facilitate NO_3RR . Normally, FE is calculated through the comparison of consumed electrons for ammonia production and the total electrons consumed during NO_3RR process, and usually expressed in percentage (%). Therefore, obtaining accurate measurements of ammonia yields is essential for the evaluation of the selectivity of this reaction. On the other hand, the ammonia yield rate commonly refers to the rate of ammonia production during the NO_3RR process. Typically, this value expresses the quantity of ammonia generated per unit of time, which provides a measure of the productivity of ammonia through the NO_3RR process. Although both these parameters are crucial for assessing the performance of NO_3RR , differences exist between them. The ammonia yield rate measures the absolute amount of ammonia produced and is a direct measurement of productivity, whereas Faraday efficiency focuses more on the information about the selectivity in the NO_3RR process towards ammonia. Besides, the potential (normally expressed as volts vs. reversible hydrogen electrode) at a certain current density refers to the required electrode potential to reach a specific reaction rate of NO_3RR , which plays a crucial role in describing the kinetics of the reaction. This potential also has a significant effect on the overall efficiency of the NO_3RR process. Energy efficiency (EE) in NO_3RR refers to the ability to use energy entering the system for ammonia production and is usually expressed in percentage (%). It is worth noting that, unlike the above evaluation metrics, EE evaluates the overall energy efficiency of the entire system, whereas, for comparison, FE focuses on the electrochemical processes of the NO_3RR .

The FE for ammonia production can be calculated based on the equation below:

$$\text{FE} = \frac{n \times c \times V \times F}{Q}$$

The yield rate of ammonia can be calculated with the equation below:

$$Y_{\text{NH}_3} = \frac{c}{t}$$

The EE for ammonia production can be calculated based on the equation below:

$$\text{EE} = \frac{\text{FE} \times E^0}{U}$$



In the above equations, n is the electron transfer number of the reaction required to form ammonia ($n = 8$ for NO_3RR); c is the concentration of the product (mol mL^{-1}); t is the reaction time (h); F is the Faraday constant ($F = 96485 \text{ C mol}^{-1}$); V is the volume of cathode electrolyte in the H-cell reactor (mL); Q is the total amount of charge consumed (C); E^0 is the theoretical electric potential difference of the reactor (V); and U is the practical voltage of the reactor (V).

Various techniques such as ^1H NMR, UV-vis spectroscopy, and ion chromatography (IC) should be applied in ammonia detection to eliminate interference or contamination from the environment or the catalyst itself.⁴⁵

In addition to the diversity in products, NO_3RR to ammonia is a complicated process involving a wide variety of intermediates. Meanwhile, the composition and structure of some electrocatalysts' surfaces will also change during the electrochemical reaction process.³⁵ Thus, classical *ex situ* electrochemical methods are inadequate to clarify the mechanism of various ammonia production pathways as they can only provide indirect information about the reaction. This motivates the development of *in situ* methods for characterizing electrode active species and reactive intermediates.¹³⁵ In contrast to the *ex situ* methods, the most crucial feature of the *in situ* technique is that it provides direct and accurate information, which contributes to the identification of changes in the process under different conditions.

Therefore, this section will mainly discuss the state-of-the-art methods for ammonia detection and *in situ* characteristic techniques for electrocatalytic synthesis of ammonia. The structure of this section is shown schematically in Fig. 12.

4.1. Ammonia detection

Based on the Lambert-Beer law, UV-vis spectroscopy is a quantitative technique that can be used to measure the concentration of a chemical substance through light absorption at a typical wavelength in gases and solutions.¹³⁶ The detected substances can be quantified using a calibration curve based on standard samples. In ammonia detection, UV-vis is the most common method due to its low cost and simple operation.⁴² Before the absorption test, chromogenic agents are required and the indophenol blue method is one of the widely used

colourimetric methods, which requires three reagents: a potassium sodium tartrate-salicylic acid solution, sodium hypochlorite solution, and sodium nitroferrocyanide solution.⁸⁹ The indophenol blue maximum absorbance could be measured at around 653 nm.¹³⁷ Another commonly used chromogenic agent is Nessler's reagent, and the maximum absorbance is usually measured at around 420 nm. However, the maximum absorbance wavelength is not a fixed figure and is affected by the pH of the solution and the differences in the spectrometer itself.¹³⁸ Besides, the concentration of the detected substance should be adjusted to the suitable absorption range of each spectrometer. Thus, the errors that may occur during the preparation of the solution are magnified many-fold during the dilution procedure, requiring extra precautions.

IC is another common method for ammonia detection, employing the principle of ion exchange. Similarly, the electrolyte should be diluted to the detection range, and pre-treatment is required to avoid the contamination and damage of the equipment by organic substances and heavy metal ions.¹³⁹ The results of IC should be quantitatively close to those of UV-vis, thus confirming the accuracy and reliability of both methods.¹³⁴

Although the common methods can detect ammonia concentration with relative accuracy, an isotopic labeling experiment using ^1H NMR is prominent in determining the N-source of the product. Zhao *et al.* introduced the atomically dispersed bimetallic Fe-Co electrocatalysts for electrocatalytic nitrogen reduction to ammonia with an extraordinary Faradaic efficiency of $79.0 \pm 3.8\%$.⁵⁹ The isotopic labelling experiment confirmed the high selectivity of NRR, which was performed using $^{15}\text{N}_2$ and $^{14}\text{N}_2$ saturated in a 0.1 M Na_2SO_4 electrolyte at -0.30 V (vs. RHE) and undergoing reaction for 2 hours. D_2O was used as a solvent for the dissolution of internal standards. For qualification, three characteristic peaks appear when using ^{14}N as the source of nitrogen, and only two peaks appear when using ^{15}N .¹⁴⁰ For quantification, the yields of $^{15}\text{NH}_4^+$ and $^{14}\text{NH}_4^+$ were calibrated with the standard curves.¹⁴¹ The closely approximated values of $^{15}\text{NH}_4^+$ and $^{14}\text{NH}_4^+$ implied that the ammonium produced in this reaction originated from the Fe-Co electrocatalyzed nitrogen reduction.



Fig. 12 The schematic illustration of state-of-the-art methods for ammonia detection and *in situ* characteristic techniques.



Besides, the concentration of reactants and by-products should also be clarified when measuring ammonia production performance. For liquid substances, *e.g.*, nitrate and nitrite, IC is mainly adopted, and the gaseous products can be typically quantified using gas chromatography (GC).¹⁴² In all these measurements, repeats of over 3 times should be performed to ensure dependability.

4.2. Intermediates of reactions

Due to the complicated electron pathway involved in electrocatalytic synthesis of ammonia,^{19,60} divergent intermediates are formed in this process, which increases the difficulties of elucidating the overall reaction mechanism. Appropriate *in situ* characterization methods are essential for understanding electrocatalytic processes at the molecular level and should be applied depending on different situations.

4.2.1. *In situ* Fourier transformed infrared spectroscopy measurement. FTIR is a technique used to obtain an infrared spectrum of the absorbance or emittance of a sample to be analyzed.¹⁴³ In this method, the functional group and the original peak related to the typical molecules can be detected, helping in identifying the structure and composition of the substances accordingly.^{138,139}

In situ FTIR, pioneered by Bewick *et al.* in the 1980s is effective in the detection of the adsorbates, molecules, and reaction intermediates.^{144–148} In ammonia production reactions, usually, *in situ* FTIR is employed to differentiate the reactive intermediates adsorbed on the catalyst electrodes. Liu *et al.* applied this technique in the mechanism study of nitrate reduction to ammonia.⁸³ In Liu's work, a novel electrocatalyst consisting of Rh single-atoms and clusters dispersed on Cu nanowires was synthesized and demonstrated to exhibit high-activity and high-selectivity for the electrocatalytic synthesis of ammonia. The results of *in situ* infrared spectroscopy clearly showed that only a weak peak related to $-\text{NH}_2$ could be detected for Cu nanowires, while after introducing Rh single-atoms/clusters to the electrocatalyst, an obvious peak of $-\text{NH}_2$ could be detected. Through the comparison of the results, the authors suggested that the introduction of Rh improved the H-surface absorption drastically, indicating that the hydrogenation step of this electrocatalyst was no longer the rate-limiting step of the nitrate reduction process (Fig. 13). This hypothesis regarding the mechanism was identical to the results of ^1H NMR, *in situ* DEMS, *in situ* EPR spectra, *etc.* The mechanism and pathway of the whole reaction were proposed based on these results with the aid of DFT calculations.

4.2.2. *In situ* differential electrochemical mass spectrometry measurement. Differential mass spectrometry (DEMS), an online detection method, is widely used to continuously identify the products and intermediates in Faradic reactions.¹⁴⁹ Nowadays, DEMS plays a significant role in not only qualitative but also quantitative¹⁵⁰ studies of the mechanism of electrocatalytic reactions. The DEMS system contains an electrochemical reaction device, a membrane inlet system and a mass spectrometer.¹⁵¹ The volatile intermediates and products produced during the electrochemical reaction enter the vacuum



Fig. 13 Electrochemical *in situ* infrared spectroscopy (IR) of Rh@Cu-0.6% and Cu NWs under different potentials in a 0.1 M Na_2SO_4 electrolyte (pH 11.5) with 0.1 M KNO_3 by Liu *et al.* Reprinted with permission from ref. 83 Copyright 2022 Wiley-VCH GmbH.

channel of the mass spectrometer through the hydrophobic membrane interface, where the mass spectrometer records the currents of different ions over time.

Yao *et al.* conducted further DEMS measurements to confirm the molecular formula of N_2H_x .¹⁵² In Yao's work, DEMS was employed to explore the mechanism of nitrogen and nitrate reduction on the surface of rhodium. The signal of H_2^+ ($m/z = 2$) and N_2H_2 ($m/z = 29$ for N_2H^+ and 30 for N_2H_2^+) was detected from 0.4 V to -0.4 V on an Rh-film electrode in both 0.1 M KOH and 0.1 M KNO_3 solutions (Ar-saturated) and in 0.1 M KOH solution (N_2 -saturated) for nitrate reduction and nitrogen reduction, respectively. The signals for H_2^+ ($m/z = 2$) and N_2H^+ ($m/z = 29$) could be detected in both reactions, while the signals for N_2H_2^+ ($m/z = 30$) were only detected in the nitrate reduction reaction (Fig. 14). The results implied that N_2H_x served as an intermediate in both nitrate reduction and nitrogen reduction. At the same time, the selectivity of NRR was lower than that of nitrate reduction to ammonia, as indicated by comparison of the signals of N_2H^+ ($m/z = 29$).

4.2.3. *In situ* shell isolated nanoparticle enhanced Raman spectroscopy measurement. Surface-enhanced Raman spectroscopy (SERS), first reported by Fleischmann in 1974, was a great breakthrough in the research and development of Raman spectroscopy for solving the problem of low sensitivity.^{153,154} Based on SERS, the isolated nanoparticle enhanced Raman spectroscopy (SHINERS) extending the universality of substrate materials and surface topography,¹⁵⁵ has developed into an effective characterization tool for catalysis in recent years. The Au@ SiO_2 core-shell structured nanoparticles not only enhance the signals of Raman spectroscopy but also inhibit the photocatalytic side reactions from the analytes.¹⁵⁶

As a state-of-the-art branch in Raman spectroscopy techniques, *in situ* SHINERS measurement is often applied in identifying the reactive intermediates on the catalyst surfaces in the





Fig. 14 (a) DEMS of H_2^+ ($m/z = 2$), N_2H^+ ($m/z = 29$), and N_2H_2^+ ($m/z = 30$) on Rh/C during a scan from 0.4 to -0.4 V in an Ar-saturated 0.1 M KOH + 0.1 M KNO_3 solution (2.5 mV s^{-1}). (b) DEMS of H_2^+ ($m/z = 2$), N_2H^+ ($m/z = 29$), and N_2H_2^+ ($m/z = 30$) on Rh/C during a scan from 0.4 to -0.4 V in a N_2 -saturated 1 M KOH solution (5 mV s^{-1}). Reprinted with permission from ref. 152 Copyright 2020 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim.

area of electrochemical catalysis due to its accuracy and stability.³⁵ Until now, many researchers have applied SHINERS to study the mechanisms, including the hydrogen evolution reaction, oxygen reduction reaction, CO reduction/oxidation reaction, nitrate reduction reaction, *etc.*¹⁵⁶ For the nitrate reduction reaction, Jr *et al.* used SHINERS to reveal a series of reactive intermediates involved in the process of nitrate reduction, such as NO_2^- and HNO .¹¹³ Specifically, in Jr's work, the intermediates of nitrate reduction were observed by SHINERS on three crystal planes of copper, which were Cu (100), Cu (111) and Cu (110), respectively. The intermediates observed on the three planes were similar, thus indicating the same mechanism and reaction pathway. Each peak of SHINERS was analyzed in detail and assigned to a reactive intermediate. As shown by the results, the mild intensity peaks at 509 cm^{-1} and 619 cm^{-1} could be assigned to the formation of Cu_2O due to partial oxidation. Two characteristic peaks could be observed in Cu (110) and Cu (111) but not in Cu (100), indicating the low formation rate of Cu_2O on Cu (100), which was a key active species on the electrode surface. The LSV curves were in accordance with this explanation for the relatively inactive nitrate reduction performance of Cu (100).¹⁵⁷

Furthermore, this method investigated the mechanism behind the decrease in nitrate reduction performance caused by chloride ions. Cl^- is known to form a chloride array on the surface of Cu at around -0.3 V vs. RHE , which has been demonstrated to impede the copper-based nitrate reduction.⁶⁵ SHINERS verified this phenomenon and gave a detailed reaction pathway in this work (Fig. 15). According to the results of SHINERS, there was no evidence of adsorption of nitrite or

nitroxyl species when the potential was scanned from 0 mV to 800 mV compared to the Cl^- free system. Instead, weak peaks associated with NH_4^+ and NH_3 appeared at around -0.5 V vs. RHE on Cu (100), thus implying a different pathway for nitrate reduction on chloride-decorated copper electrodes. Also, as a high-sensitive surface detection technique, SHINERS could be used in the detection of active species on the electrode surfaces, which is discussed in the next section.

In addition to the three *in situ* characterization methods mentioned above, there are some other techniques applied in the *in situ* analysis of reactive intermediates. *In situ* IC is a technique based on traditional IC and is conducted to detect the ions generated or consumed over time. Moreover, a fully automated and low-cost IC system for *in situ* analysis of nitrite and nitrate in natural waters was reported in 2020 by Paull *et al.*¹⁵⁸ *In situ* electron spin resonance (ESR) is a microwave absorption spectroscopy technique used to detect and study paramagnetic substances containing unpaired electrons. Hydrogen radicals play an important role in the reduction of nitrate to ammonia and can be monitored with *in situ* ESR to help elucidate the mechanism of the reaction.⁷⁵

In brief, with the development of *in situ* techniques, more and more new methods are widely used to explain complex catalytic mechanisms.

4.3. Active species on electrode surfaces

Since electrochemical processes are investigated at the interface between a liquid electrolyte and a solid electrode,¹⁵⁹ identifying and thoroughly exploring the active species on the electrode surface are important. The common *ex situ*





Fig. 15 (a) Adsorption modes of nitrite, nitric oxide, and HNO on the Cu surface. Electrochemical *in situ* SHINERS spectra collected from (b) Cu (100), (c) Cu (111), and (d) Cu (110) in a 0.1 M HClO₄ solution with 0.05 M HNO₃ and 10 mM HCl at a potential between 0 and -0.8 V vs. Ag/AgCl. Reprinted with permission from ref. 157 Copyright 2016 Elsevier Ltd.

characterization studies for electrode materials can only give the static result rather than continuous analysis during dynamic reaction processes. In this regard, electrochemical *in situ* characterization studies for active species are crucial for studying and designing the electrocatalyst.

4.3.1. *In situ* Raman spectroscopy measurement. *In situ* Raman spectroscopy is a powerful method for the identification of active species due to the unlimited pressure, temperature, or the presence of reaction gases during the measurement process.¹⁶⁰ Theoretically, Raman spectroscopy can reveal the structure information of substances on micro-scales, which is characterized by frequency shifts. Although the Raman spectroscopy signal is relatively weak for species adsorbed on the surface, it is very effective for the analysis of species on the electrode surface. By combining the features of Raman spectroscopy with electrochemistry, the structure and composition

evolution of the electrocatalyst surface could be characterized clearly.¹⁶¹

Normally, electrochemical *in situ* Raman spectroscopy measurements are carried out with a Raman apparatus and *in situ* Raman cells connected to an electrochemical workstation.³⁵ As a critical component, the *in situ* Raman cell was once a major limitation in performing this measurement.¹⁶² Nowadays, an *in situ* Raman cell usually contains a working electrode, a counter electrode, a reference electrode, and a quartz optical window. To avoid corrosion of the solution and erosion of the instrument by gases, the Raman cell must be equipped with a sealing system for the optical window. Intervention from the solution signal under experimental conditions should be avoided as much as possible by using a thin layer of solution (0.1–1 mm between the electrode and the window), which is important for microscopic Raman systems. Thick optical



windows or solution layers might cause changes in the optical path of the microscope system and degrade the collection efficiency of the surface Raman signal.

Fang *et al.* applied SHINERS spectra in probing both the surface of the catalyst and the reduced intermediates adsorbed during the NO₃RR process.⁹² The spectra between 230–750 cm⁻¹ on Cu₅₀Co₅₀, Cu, and Co mainly clarified the chemical properties of the catalyst on the surface. As shown in Fig. 16, the characterization peaks belonging to Cu₂O (625 cm⁻¹) can be observed when the potential is over 0.6 V in Cu₅₀Co₅₀ and Cu. However, when the potential decreased, the peaks for the oxides gradually shrank. The reduction to the metallic state (Cu) even before the NO₃RR indicated that the surface of the catalyst was partially oxidized by the air and the real active sites for NO₃RR were metal Cu and Co. Besides, the peaks at 431 cm⁻¹ and 568 cm⁻¹ could be assigned to Cu–O_x and Co–O_x caused by the adsorption of oxynitride on the catalyst surface, respectively.^{163,164} The spectra between 750–1700 cm⁻¹ clarified the signals of nitrate and intermediates adsorbed on the surface. With the potential shift from open circuit potential (OCP) to –0.1 V, the peaks for nitrate and intermediates appeared sequentially. In this way, the deoxygenation pathway was proposed to occur in the sequence of NO₃⁻ → *NO₃ → *NO₂ → *NO, while the hydrogenation pathway was suggested to occur in the sequence of *NO → *NOH → *NH₂OH → *NH₃ → NH₃. Moreover, by comparing the peaks on Cu₅₀Co₅₀ and Cu, the peak related to NO₂⁻ appeared only on the Cu surface, suggesting its poor ability for further deoxygenation of nitrite.

Wang *et al.* investigated the reactive species involved in nitrate reduction for ammonia production through the *in situ* Raman test.⁸⁹ The initial Raman spectrum of the island-like copper structure indicated the existence of Cu₂O and a small amount of CuO. With the reduction reaction happening on the electrode surface, the peak of CuO disappeared immediately after applying a negative potential, while the intensity of the peaks for Cu₂O first increased to the maximum value and then

decreased gradually with the negative shift in potential. Thus, it can be concluded that CuO was first reduced to Cu₂O and then reduced further to Cu along with the reaction of nitrate reduction to ammonia. The conclusion above suggested that the real active sites for nitrate reduction were Cu₂O formed during the reduction process rather than CuO on the initial electrode.

In addition, Zhang *et al.* reported an efficient electrocatalyst for green ammonia production starting from CuO nanowire arrays, which were then *in situ* converted into Cu/Cu₂O nanowire arrays during the reduction process of nitrate to ammonia.⁵⁰ The speculation regarding active sites was also confirmed by *in situ* Raman spectroscopy measurement, which was in accordance with Li's work.

4.3.2. *In situ* X-ray absorption spectroscopy measurement.

X-ray absorption spectroscopy (XAS) measurement, based on the X-ray absorption edge of elements which was first observed by Maurice de Broglie in 1913,¹⁶⁵ has become an advanced technique to study complex and faceted materials. The principle of XAS is based on the relationship between the X-ray's intensity degradation and the materials' structure and composition. XAS studies the relationship between the transmitted intensity and the incident intensity. Since the transmitted light intensity is related to the elemental and atomic mass, it can be used for qualitative and even quantitative analysis of elements. Depending on the formation mechanism and the shape of the peaks, XAS can be sorted into X-ray absorption near edge structure (XANES) and extended X-ray absorption fine structure (EXAFS), each corresponding to low-energy photon absorption and high-energy photon absorption, respectively.

Chen *et al.* adopted XAS measurement to provide a deeper understanding of the electronic properties of the Cu-based electrocatalyst (Ru-CuNW).⁷⁷ The Ru-dispersed Cu nanowire catalyst with outstanding performance was reported to reach an industrial-grade current of 1 A cm⁻² for nitrate reduction to ammonia while retaining high selectivity (FE of 93%). To clarify the structure and composition of the high-performance



Fig. 16 SHINERS spectra between 230–750 cm⁻¹ on (a) Cu₅₀Co₅₀, (b) Cu, and (c) Co. (d) SHINERS spectra between 750–1700 cm⁻¹ on Cu₅₀Co₅₀ in 100 mM KNO₃ + 10 mM KOH during cathodic polarization from 0.7 to –0.1 V, by Fang *et al.* Reprinted with permission from ref. 92 Copyright 2022 Springer Nature.





Fig. 18 The schematic illustration of the practical application of nitrate-to-ammonia conversion from wastewater. Reprinted with permission from ref. 50 Copyright 2020 Wiley-VCH.

removal of nitrate with an initial concentration of $50 \text{ mg L}^{-1} \text{ N-NO}_3$.¹⁶⁹ In 2023, Wang *et al.* employed a free-standing membrane¹⁷² incorporating Cu single atoms for NO_3RR in flow-through electrofiltration.

Besides, as a significant characteristic of wastewater, inorganic ions are complicated and unavoidable. These ions include both cations and anions such as Na^+ , K^+ , Ca^{2+} , Mg^{2+} , Al^{3+} , SO_4^{2-} , Cl^- , I^- , *etc.* Some monovalent cations can promote the performance of NO_3RR by forming instantaneous neutral ion pairs, changing the bilayer structure of the cathode.¹⁶⁷ The ion pair would attract the reducing ion (nitrate), which strengthens the connection between the cathode and reducing ions and facilitates easier reduction of nitrate. Besides, the HER would be suppressed with a suitable type and number of cations due to the repulse of H^+ . Meanwhile, cations like Mg^{2+} and Ca^{2+} have a negative effect on the NO_3RR . Due to the continuous consumption of H^+ , precipitates would form on the cathode electrode, thus blocking the active sites of the reaction, which is also known as poisoning.¹⁷³ Similarly, it has been reported that SO_4^{2-} would compete with NO_3^- within a certain potential range for active sites. However, the differences in the enthalpy of adsorption for ions on particular cathodes affect the NO_3RR performance and specific situations need to be analysed on a case-by-case basis.^{29,174}

In the context of wastewater treatment application, there exists a substantial scope for advancement and scholarly investigation. This includes the exploration of the effects of low nitrate concentrations. Concurrently, the introduction of inorganic ions into the process presents another significant area for academic inquiry, underscoring the importance of these issues in the field.

5.2. Scaling-up application

Usually at the laboratory scale, single-chamber reactors and dual-chamber reactors (H-cell) are applied for nitrate-to-ammonia

conversion with chamber volumes ranging from 30–200 mL (Fig. 19). For industrial-scale ammonia production, the reactor configuration needs to be significantly larger, potentially hundreds of litres or even cubic meters in size. Additionally, the electrolyte should be in a flow mode to ensure a continuous and sufficient supply of nitrate for the conversion process.

Some recent works have taken this consideration further towards industrial applications. Xu *et al.* designed a bipolar membrane reactor for continuous electro-synthesis of ammonia from 2000 ppm nitrate (equivalent to 0.034 M).¹⁷⁵ In order to achieve ionic equilibrium, a bipolar membrane nitrate reduction process was proposed and the hydrolysis dissociation sites were increased by constructing a three-dimensional physically interlocking interface for the bipolar membrane in this work. The system finally realized a stable ammonia production of over 100 h at 1000 mA cm^{-2} with a Faradaic efficiency of 86.2% and a maximum yield rate of $68.4 \text{ mg h}^{-1} \text{ cm}^{-2}$. The schematic for a bipolar membrane reactor with a serpentine flow field supplying fresh electrolyte is shown in Fig. 19(c). Earlier, in 2021, Zheng *et al.* made the first trial and constructed a prototype reactor of 500 L for converting nitrate from real chemical wastewater to ammonia, realizing a FE of 90.4% at $2000 \text{ mg L}^{-1} \text{ N-NO}_3$.¹⁷⁶ In this prototype reactor, two electrode stacks with 13 electrode sheets form the electrode module, fully immersed in the electrolyte tank. This electrode module originated in the field of bioelectrochemistry and has the advantage of not only alleviating the problem of limited capacity and reaction sites but also avoiding concentration fluctuations due to high space utilization.^{176,177}

To sum up, the scaling-up production of ammonia from nitrate reduction has not been much studied to date, and further research on the design of the electric stack in particular is highly warranted. Exploring advanced electrode materials, scalable reactors and cost-effective control systems can contribute to enhancing the performance and efficiency of the





Fig. 19 The schematic illustration of (a) single-chamber reactor and (b) dual-chamber reactor. Reprinted with permission from ref. 167 Copyright 2023 Elsevier B.V. (c) Bipolar membrane reactor for ammonia electro-synthesis in a flow mode. Reprinted with permission from ref. 176 Copyright 2023 Springer Nature. (d) Prototype stack reactor for nitrate-to-ammonia conversion. Reprinted with permission from ref. 175 Copyright 2021 American Chemical Society.

stack, ultimately advancing the scaled-up production of ammonia.¹⁷⁸

5.3. Economic analysis

As mentioned above, the economic effect is a critical part of industrial application of nitrate-to-ammonia conversion.

The economic benefits of this strategy are listed below. First, compared with the traditional Haber–Bosch method, which is also the current mainstream for ammonia production, the nitrate-to-ammonia conversion is more sustainable and applicable for inexpensive renewable electricity. Second, it enables the concept of turning waste into treasure. Nitrate pollution is common in various types of wastewater with a normal range of 10–200 mg L⁻¹ N-NO₃,¹⁶⁸ while this value could even exceed 1000 mg L⁻¹ N-NO₃ in some industries like fertilizer, metal, explosives, *etc.* Third, compared to NRR, the performance of NO₃RR in the lab is much closer to the practical requirements, with the pilot breaking through the laboratory barriers.

Specifically, the economic cost of nitrate-to-ammonia conversion mainly includes the initial cost of system construction and installation, operation and maintenance, monitoring and compliance. Among them, energy consumption and the cost of electrode materials are regarded as two crucial factors for the application process.

At this early stage of practical application, several research works pay attention to economic analysis. McEnaney *et al.* performed a preliminary techno-economic analysis considering only the electricity cost for ammonium nitrate production.¹⁷⁹ In this work, preliminary techno-economic considerations suggest that the pathway for recycling spent nitrate into ammonium

products is promising and that full conversion to ammonia may be feasible if electricity consumption is sufficiently low. However, the capital costs, price of electricity, and cell efficiency are estimated with given prices and the authors also mentioned that these practical values should be considered for further exploration. Gao *et al.* studied the economic cost of energy consumption based on an energy-related parameter, which is determined by power and ammonia yield.¹⁸⁰ In this work, a profitable region is given where higher nitrate concentration and lower electricity cost are beneficial. It is worth mentioning that this nitrate-to-ammonia process also eliminates nitrate pollution, whereas the normal nitrification/denitrification process is assumed to have an estimated cost of \$15.56 per kg-N removed.¹⁸¹ From the perspective of nitrate removal, Wang *et al.* predicted the energy consumption of this strategy using the Cu/Ti electrode and Cu/GO/Ti electrode, which are 0.82 kW h g⁻¹ nitrate-N and 0.47 kW h g⁻¹ nitrate-N, respectively. According to the average industrial electricity cost at present (\$0.005 per kW h), the cost of electricity consumption using Cu/GO/Ti electrodes is estimated to be \$2.35 per kg-N removed.¹⁸⁰

Although electrodes are a key component of the reactor, their economic analysis is not sufficiently conducted. Cu-based catalysts have been widely recognized for their high activity and selectivity in nitrate-to-ammonia conversion. Meanwhile, the price for the brass mesh (65% of Cu) is \$5.7–22.9 per m², which is undoubtedly suitable for industrial applications. Besides, another factor closely related to the cost of the electrode is the durability of the material itself, which should be taken into consideration on a case-by-case basis in the economic analysis.



In conclusion, the current reports reveal to some extent the great promise of this nitrate-to-ammonia strategy, but it is difficult to arrive at an accurate assessment because of the gaps in the relevant economic analysis. For the future, it is recommended to conduct a detailed feasibility study considering all the factors mentioned above to achieve an accurate economic analysis.

6. Conclusion and outlook

Electrocatalytic ammonia production from nitrate (NO_3RR) is promising and highly attractive due to its ambient reaction condition, low energy consumption, and zero CO_2 emission. This review summarized the recent progress in elucidating the mechanism of NO_3RR , state-of-the-art Cu-based catalysts for NO_3RR , corresponding analysis methods for product detection, practical applications and economic analysis conducted to date.

In recent years, significant attempts have been made by researchers to design and develop efficient and low-cost catalysts for this reaction. Cu-based catalysts certainly show outstanding kinetics along with selectivity towards ammonia synthesis. Most current research works mainly focus on higher FE and smaller overpotentials, aiming to improve ammonia yield and ammonia selectivity. Among them, nanomaterials with finite structures expose more active sites through a larger specific surface area, which greatly enhances the activity of the material. Also, great achievements have been made in revealing the in-depth mechanisms of NO_3RR recently. On one hand, theoretical calculations give insights into the reaction pathways and rationalize a series of experimental observations. Moreover, the activity and selectivity trends of different catalysts can be simulated and summarized, providing guidance for screening and designing efficient catalysts. On the other hand, the widespread utilization of *in situ* characterization methods enables direct experimental observation during real-time reactions, providing a powerful means for unveiling the reaction intermediates and active species of the electrode surface.

Although the great potential for electrochemical ammonia production *via* nitrate reduction has been proven, it is still far from the real-environment application and has some challenges that need to be explored and solved. First, as a significant concern in the industry, the long-term stability of Cu-based catalysts during NO_3RR should be considerably improved. Although many reported Cu-based catalysts could reach a high FE of over 90%, the problems of corrosion and dissolution still exist especially in acidic environments, leading to inferior stability. Thus, future research and development efforts should focus on optimizing the stability of copper-based catalysts. This could be achieved through various strategies, such as the use of support materials to prevent the sintering of copper particles, the incorporation of stabilizing agents to inhibit the leaching of copper ions, and the modification of the catalyst preparation method to control the oxidation state of copper. For example, it has been reported that the

single-atom Cu catalysts are more likely to present appreciable stability due to the strong interactions between Cu atoms and corresponding coordination atoms.¹⁰⁴

Second, the conventional electrode fabrication method using polymeric binders (mostly Nafion) to fix the catalyst on the electrode surface would result in inefficient catalyst utilization, reduced conductivity and weakened mass transfer. Even more, the use of expensive Nafion solution adds to the costs in the electrode preparation process, increasing the overall economic cost. Therefore, self-supported catalysts which could be directly utilized as catalytic electrodes are a promising solution to this problem.

Third, large-scale reactors should be developed to fit the practical ammonia production requirements. The magnification of the reactor enables the maximum reaction rate and significantly increases the practical ammonia yield. However, with the scaling up of the reactor, it becomes important to comprehensively consider achieving ideal FE, energy efficiency, and economic efficiency, which was usually neglected in lab-scale reactors. Therefore, the rational design of the reactor and optimized reaction conditions such as cell voltage, temperature, and electrolyte type/concentration should be figured out. Furthermore, an in-depth investigation of mass/charge transport mechanisms at the cell level should be thoroughly conducted.

Fourth, future research efforts should aim at developing electrocatalysts capable of efficiently converting nitrate over a wide range of concentrations, from the low concentrations typically found in groundwater (*e.g.*, 20 ppm) to the high concentrations found in industrial wastewater (*e.g.*, 1000 ppm). The development of electrocatalytic systems that effectively address this wide range of nitrate levels is critical for practical applications in environmental remediation and industrial processes.

Last but not least, insights into the economic estimations in a professional and detailed way should be employed, including the cost of energy consumption, catalyst consumption, reactor construction, *etc.*

In conclusion, developing electrocatalytic ammonia production reactions from a lab scale to a practical scale will become the trend of research in this field. The development of electrocatalytic ammonia production *via* nitrate reduction will revolutionize the future sustainable ammonia economy, with Cu-based catalysts as the foundation.

Author contributions

L. A. proposed the topic of the review. X. Z. proposed the outline of the review. K. Z. drafted the manuscript. All authors contributed to the editing of the manuscript.

Conflicts of interest

The authors declare no conflict of interest.



Acknowledgements

We acknowledge the support from the National Natural Science Foundation of China (no. 22205187), Hong Kong Polytechnic University (CD4D and WZ4Q), and a grant received from the Research Institute for Smart Energy (CDA4) at The Hong Kong Polytechnic University.

References

- J. G. Chen, R. M. Crooks, L. C. Seefeldt, K. L. Bren, R. M. Bullock, M. Y. Darensbourg, P. L. Holland, B. Hoffman, M. J. Janik and A. K. Jones, *Science*, 2018, **360**, eaar6611.
- D. Saygin, H. Blanco, F. Boshell, J. Cordonnier, K. Rouwenhorst, P. Lathwal and D. Gielen, *Sustainability*, 2023, **15**, 1623.
- S. Chatterjee, R. K. Parsapur and K.-W. Huang, *ACS Energy Lett.*, 2021, **6**, 4390–4394.
- V. Smil, *Enriching the Earth: Fritz Haber, Carl Bosch, and the Transformation of World Food Production*, MIT Press, 2004.
- M. Capdevila-Cortada, *Nat. Catal.*, 2019, **2**, 1055.
- E. Meloni, G. Iervolino, C. Ruocco, S. Renda, G. Festa, M. Martino and V. Palma, *Energies*, 2022, **15**, 3588.
- B. H. Suryanto, H.-L. Du, D. Wang, J. Chen, A. N. Simonov and D. R. MacFarlane, *Nat. Catal.*, 2019, **2**, 290–296.
- Y. Chen, H. Liu, N. Ha, S. Licht, S. Gu and W. Li, *Nat. Catal.*, 2020, **3**, 1055–1061.
- D. R. MacFarlane, P. V. Cherepanov, J. Choi, B. H. Suryanto, R. Y. Hodgetts, J. M. Bakker, F. M. F. Vallana and A. N. Simonov, *Joule*, 2020, **4**, 1186–1205.
- M. C. Etter, *Acc. Chem. Res.*, 1990, **23**, 120–126.
- H. Liu, H. Wang and J. Xu, *CIESC J.*, 2022, **73**, 32–45.
- B. Han, J. Liu, C. Lee, C. Lv and Q. Yan, *Small Methods*, 2023, 2300277.
- C. Lv, C. Yan, G. Chen, Y. Ding, J. Sun, Y. Zhou and G. Yu, *Angew. Chem.*, 2018, **130**, 6181–6184.
- S. Chen, S. Perathoner, C. Ampelli, C. Mebrahtu, D. Su and G. Centi, *Angew. Chem., Int. Ed.*, 2017, **56**, 2699–2703.
- M. Khalid, M. R. Hatshan, A. M. B. Honorato, B. Kumar and H. Varela, *Nanomaterials for Electrocatalysis*, Elsevier, 2022, pp. 317–334.
- S. Z. Andersen, V. Čolić, S. Yang, J. A. Schwalbe, A. C. Nielander, J. M. McEnaney, K. Enemark-Rasmussen, J. G. Baker, A. R. Singh and B. A. Rohr, *Nature*, 2019, **570**, 504–508.
- C. Tang and S.-Z. Qiao, *Chem. Soc. Rev.*, 2019, **48**, 3166–3180.
- Z. Geng, Z. Chen, Z. Li, X. Qi, X. Yang, W. Fan, Y. Guo, L. Zhang and M. Huo, *Dalton Trans.*, 2018, **47**, 11104–11112.
- H. Shen, C. Choi, J. Masa, X. Li, J. Qiu, Y. Jung and Z. Sun, *Chem*, 2021, **7**, 1708–1754.
- P. Wei, J. Liang, Q. Liu, L. Xie, X. Tong, Y. Ren, T. Li, Y. Luo, N. Li and B. Tang, *J. Colloid Interface Sci.*, 2022, **615**, 636–642.
- M. J. Moorcroft, J. Davis and R. G. Compton, *Talanta*, 2001, **54**, 785–803.
- B. T. Nolan, K. J. Hitt and B. C. Ruddy, *Environ. Sci. Technol.*, 2002, **36**, 2138–2145.
- P. H. van Langevelde, I. Katsounaros and M. T. Koper, *Joule*, 2021, **5**, 290–294.
- S. Garcia-Segura, M. Lanzarini-Lopes, K. Hristovski and P. Westerhoff, *Appl. Catal., B*, 2018, **236**, 546–568.
- Y. Wang, Y. Yu, R. Jia, C. Zhang and B. Zhang, *Natl. Sci. Rev.*, 2019, **6**, 730–738.
- M. Karamad, T. J. Goncalves, S. J. Villegas, I. Gates and S. Siahrostami, *Faraday Discuss.*, 2023, **243**, 502–519.
- H. Shin, S. Jung, S. Bae, W. Lee and H. Kim, *Environ. Sci. Technol.*, 2014, **48**, 12768–12774.
- L. Mattarozzi, S. Cattarin, N. Comisso, R. Gerbasi, P. Guerriero, M. Musiani and E. Verlatto, *Electrochim. Acta*, 2017, **230**, 365–372.
- G. Dima, A. De Vooyos and M. Koper, *J. Electroanal. Chem.*, 2003, **554**, 15–23.
- D. Reyter, D. Bélanger and L. Roué, *J. Hazard. Mater.*, 2011, **192**, 507–513.
- J. F. Su, I. Ruzybayev, I. Shah and C. Huang, *Appl. Catal., B*, 2016, **180**, 199–209.
- O. Peng, Q. Hu, X. Zhou, R. Zhang, Y. Du, M. Li, L. Ma, S. Xi, W. Fu and Z.-X. Xu, *ACS Catal.*, 2022, **12**, 15045–15055.
- T. Hu, C. Wang, M. Wang, C. M. Li and C. Guo, *ACS Catal.*, 2021, **11**, 14417–14427.
- H. Wan, A. Bagger and J. Rossmeisl, *Angew. Chem.*, 2021, **133**, 22137–22143.
- Y. Wang, C. Wang, M. Li, Y. Yu and B. Zhang, *Chem. Soc. Rev.*, 2021, **50**, 6720–6733.
- M. De Groot and M. Koper, *J. Electroanal. Chem.*, 2004, **562**, 81–94.
- R. Lange, E. Maisonhaute, R. Robin and V. Vivier, *Electrochem. Commun.*, 2013, **29**, 25–28.
- D. Sicsic, F. Balbaud-Céli er and B. Tribollet, *Eur. J. Inorg. Chem.*, 2014, 6174–6184.
- I. Katsounaros, *Curr. Opin. Electrochem.*, 2021, **28**, 100721.
- K. Vetter, *Z. Elektrochem.*, 1959, **63**, 1189–1191.
- E. Abel, H. Schmid and J. Schafranik, *Z. Phys. Chem.*, 1931, **1931**, 510–522.
- D. Anastasiadou, Y. van Beek, E. J. Hensen and M. Costa Figueiredo, *Electrochem. Sci. Adv.*, 2022, e2100220.
- M. G. De Chialvo and A. Chialvo, *Electrochim. Acta*, 1998, **44**, 841–851.
- D. Xu, Y. Li, L. Yin, Y. Ji, J. Niu and Y. Yu, *Front. Environ. Sci. Eng.*, 2018, **12**, 1–14.
- X. Lu, H. Song, J. Cai and S. Lu, *Electrochem. Commun.*, 2021, **129**, 107094.
- J. Mart nez, A. Ortiz and I. Ortiz, *Appl. Catal., B*, 2017, **207**, 42–59.
- X. Deng, Y. Yang, L. Wang, X. Z. Fu and J. L. Luo, *Adv. Sci.*, 2021, **8**, 2004523.
- T. Ren, K. Ren, M. Wang, M. Liu, Z. Wang, H. Wang, X. Li, L. Wang and Y. Xu, *Chem. Eng. J.*, 2021, **426**, 130759.
- J. Gao, B. Jiang, C. Ni, Y. Qi and X. Bi, *Chem. Eng. J.*, 2020, **382**, 123034.



- 50 Y. Wang, W. Zhou, R. Jia, Y. Yu and B. Zhang, *Angew. Chem., Int. Ed.*, 2020, **59**, 5350–5354.
- 51 D. Hao, Z.-g Chen, M. Figiela, I. Stepniak, W. Wei and B.-J. Ni, *J. Mater. Sci. Technol.*, 2021, **77**, 163–168.
- 52 J.-X. Liu, D. Richards, N. Singh and B. R. Goldsmith, *ACS Catal.*, 2019, **9**, 7052–7064.
- 53 F. Wang, Y. p Liu, H. Zhang and K. Chu, *ChemCatChem*, 2019, **11**, 1441–1447.
- 54 X. Nie, M. R. Esopi, M. J. Janik and A. Asthagiri, *Angew. Chem.*, 2013, **125**, 2519–2522.
- 55 X. Nie, W. Luo, M. J. Janik and A. Asthagiri, *J. Catal.*, 2014, **312**, 108–122.
- 56 T. F. Jaramillo, K. P. Jørgensen, J. Bonde, J. H. Nielsen, S. Horch and I. Chorkendorff, *Science*, 2007, **317**, 100–102.
- 57 J. Greeley, T. F. Jaramillo, J. Bonde, I. Chorkendorff and J. K. Nørskov, *Nat. Mater.*, 2006, **5**, 909–913.
- 58 Z.-Y. Wu, M. Karamad, X. Yong, Q. Huang, D. A. Cullen, P. Zhu, C. Xia, Q. Xiao, M. Shakouri and F.-Y. Chen, *Nat. Commun.*, 2021, **12**, 2870.
- 59 S. Zhang, M. Han, T. Shi, H. Zhang, Y. Lin, X. Zheng, L. R. Zheng, H. Zhou, C. Chen and Y. Zhang, *Nat. Sustainability*, 2022, 1–11.
- 60 A. De Vooy, R. Van Santen and J. Van Veen, *J. Mol. Catal. A: Chem.*, 2000, **154**, 203–215.
- 61 D. Çirimi, R. Aydın and F. Köleli, *J. Electroanal. Chem.*, 2015, **736**, 101–106.
- 62 A. D. McNaught and A. Wilkinson, *Compendium of Chemical Terminology*, Blackwell Science Oxford, 1997.
- 63 M. J. Liu, J. Guo, A. S. Hoffman, J. H. Stenlid, M. T. Tang, E. R. Corson, K. H. Stone, F. Abild-Pedersen, S. R. Bare and W. A. Tarpeh, *J. Am. Chem. Soc.*, 2022, **144**, 5739–5744.
- 64 Z. N. Zhang, Q. L. Hong, X. H. Wang, H. Huang, S. N. Li and Y. Chen, *Small*, 2023, 2300530.
- 65 D. Pletcher and Z. Poorabedi, *Electrochim. Acta*, 1979, **24**, 1253–1256.
- 66 L. Palmisano, V. Augugliaro, A. Sclafani and M. Schiavello, *J. Phys. Chem.*, 1988, **92**, 6710–6713.
- 67 N. Furuya and H. Yoshida, *J. Electroanal. Chem. Interfacial Electrochem.*, 1990, **291**, 269–272.
- 68 N. Furuya and H. Yoshida, *J. Electroanal. Chem. Interfacial Electrochem.*, 1989, **263**, 171–174.
- 69 Q. Wang, G. Zheng, S. Hao, X. Liu, J. Zheng, Y. Wang, Z. Su, N. Xu, Y. He and L. Lei, *ACS Sustainable Chem. Eng.*, 2019, **8**, 44–49.
- 70 L. Janssen, M. Pieterse and E. Barendrecht, *Electrochim. Acta*, 1977, **22**, 27–30.
- 71 H. Wang, Y. Li, C. Li, K. Deng, Z. Wang, Y. Xu, X. Li, H. Xue and L. Wang, *J. Mater. Chem. A*, 2019, **7**, 801–805.
- 72 H. Y. F. Sim, J. R. T. Chen, C. S. L. Koh, H. K. Lee, X. Han, G. C. Phan-Quang, J. Y. Pang, C. L. Lay, S. Pedireddy and I. Y. Phang, *Angew. Chem.*, 2020, **132**, 17145–17151.
- 73 M. I. Ahmed, C. Liu, Y. Zhao, W. Ren, X. Chen, S. Chen and C. Zhao, *Angew. Chem., Int. Ed.*, 2020, **59**, 21465–21469.
- 74 Y. Wang, A. Xu, Z. Wang, L. Huang, J. Li, F. Li, J. Wicks, M. Luo, D.-H. Nam and C.-S. Tan, *J. Am. Chem. Soc.*, 2020, **142**, 5702–5708.
- 75 J. Li, G. Zhan, J. Yang, F. Quan, C. Mao, Y. Liu, B. Wang, F. Lei, L. Li and A. W. Chan, *J. Am. Chem. Soc.*, 2020, **142**, 7036–7046.
- 76 L. Su, K. Li, H. Zhang, M. Fan, D. Ying, T. Sun, Y. Wang and J. Jia, *Water Res.*, 2017, **120**, 1–11.
- 77 F.-Y. Chen, Z.-Y. Wu, S. Gupta, D. J. Rivera, S. V. Lambeets, S. Pecaut, J. Y. T. Kim, P. Zhu, Y. Z. Finrock and D. M. Meira, *Nat. Nanotechnol.*, 2022, 1–9.
- 78 H. Jiang, G. F. Chen, O. Savateev, J. Xue, L. X. Ding, Z. Liang, M. Antonietti and H. Wang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202218717.
- 79 Z. Zhang, Y. Liu, X. Su, Z. Zhao, Z. Mo, C. Wang, Y. Zhao, Y. Chen and S. Gao, *Nano Res.*, 2023, 1–10.
- 80 M. Xie, S. Tang, Z. Li, M. Wang, Z. Jin, P. Li, X. Zhan, H. Zhou and G. Yu, *J. Am. Chem. Soc.*, 2023, **45**, 13957–13967.
- 81 P. Li, L. Liao, Z. Fang, G. Su, Z. Jin and G. Yu, *Proc. Natl. Acad. Sci.*, 2023, **120**, e2305489120.
- 82 X. Fu, X. Zhao, X. Hu, K. He, Y. Yu, T. Li, Q. Tu, X. Qian, Q. Yue and M. R. Wasielewski, *Appl. Mater. Today*, 2020, **19**, 100620.
- 83 H. Liu, X. Lang, C. Zhu, J. Timoshenko, M. Rüscher, L. Bai, N. Guijarro, H. Yin, Y. Peng and J. Li, *Angew. Chem.*, 2022, e202202556.
- 84 W. Gao, K. Xie, J. Xie, X. Wang, H. Zhang, S. Chen, H. Wang, Z. Li and C. Li, *Adv. Mater.*, 2023, **35**, 2202952.
- 85 K. Wu, C. Sun, Z. Wang, Q. Song, X. Bai, X. Yu, Q. Li, Z. Wang, H. Zhang and J. Zhang, *ACS Mater. Lett.*, 2022, **4**, 650–656.
- 86 Y. Xue, Q. Yu, Q. Ma, Y. Chen, C. Zhang, W. Teng, J. Fan and W.-x Zhang, *Environ. Sci. Technol.*, 2022, **56**, 14797–14807.
- 87 J. Yang, H. Qi, A. Li, X. Liu, X. Yang, S. Zhang, Q. Zhao, Q. Jiang, Y. Su and L. Zhang, *J. Am. Chem. Soc.*, 2022, **144**, 12062–12071.
- 88 H. Chen, C. Zhang, L. Sheng, M. Wang, W. Fu, S. Gao, Z. Zhang, S. Chen, R. Si and L. Wang, *J. Hazard. Mater.*, 2022, **434**, 128892.
- 89 C. Wang, F. Ye, J. Shen, K.-H. Xue, Y. Zhu and C. Li, *ACS Appl. Mater. Interfaces*, 2022, **14**, 6680–6688.
- 90 J. Qin, L. Chen, K. Wu, X. Wang, Q. Zhao, L. Li, B. Liu and Z. Ye, *ACS Appl. Energy Mater.*, 2021, **5**, 71–76.
- 91 Z. Gong, W. Zhong, Z. He, Q. Liu, H. Chen, D. Zhou, N. Zhang, X. Kang and Y. Chen, *Appl. Catal., B*, 2022, **305**, 121021.
- 92 J.-Y. Fang, Q.-Z. Zheng, Y.-Y. Lou, K.-M. Zhao, S.-N. Hu, G. Li, O. Akdim, X.-Y. Huang and S.-G. Sun, *Nat. Commun.*, 2022, **13**, 7899.
- 93 Y. Zhang, X. Chen, W. Wang, L. Yin and J. C. Crittenden, *Appl. Catal., B*, 2022, **310**, 121346.
- 94 C. Wang, Z. Liu, T. Hu, J. Li, L. Dong, F. Du, C. Li and C. Guo, *ChemSusChem*, 2021, **14**, 1825–1829.
- 95 X. Zhang, C. Wang, Y. Guo, B. Zhang, Y. Wang and Y. Yu, *J. Mater. Chem. A*, 2022, **10**, 6448–6453.
- 96 F. Yang, D. Deng, X. Pan, Q. Fu and X. Bao, *Natl. Sci. Rev.*, 2015, **2**, 183–201.



- 97 V. Rosca, M. Duca, M. T. de Groot and M. T. Koper, *Chem. Rev.*, 2009, **109**, 2209–2244.
- 98 D. Reyter, D. Bélanger and L. Roué, *Electrochim. Acta*, 2008, **53**, 5977–5984.
- 99 R. Li, T. Gao, W. Qiu, M. Xie, Z. Jin and P. Li, *Nano Res.*, 2023, 1–6.
- 100 Z. Li, S. Ji, Y. Liu, X. Cao, S. Tian, Y. Chen, Z. Niu and Y. Li, *Chem. Rev.*, 2019, **120**, 623–682.
- 101 Y. Liu, W. Qiu, P. Wang, R. Li, K. Liu, K. M. Omer, Z. Jin and P. Li, *Appl. Catal., B*, 2024, **340**, 123228.
- 102 M. Wang, T. Hu, C. Wang, F. Du, H. Yang, W. Sun, C. Guo and C. M. Li, *Sci. China Mater.*, 2023, 1–9.
- 103 T. Zhang, D. Zhang, X. Han, T. Dong, X. Guo, C. Song, R. Si, W. Liu, Y. Liu and Z. Zhao, *J. Am. Chem. Soc.*, 2018, **140**, 16936–16940.
- 104 T. Zhu, Q. Chen, P. Liao, W. Duan, S. Liang, Z. Yan and C. Feng, *Small*, 2020, **16**, 2004526.
- 105 S. Wang, H. Gao, L. Li, K. San Hui, D. A. Dinh, S. Wu, S. Kumar, F. Chen, Z. Shao and K. N. Hui, *Nano Energy*, 2022, **100**, 107517.
- 106 J. Zhou, F. Pan, Q. Yao, Y. Zhu, H. Ma, J. Niu and J. Xie, *Appl. Catal., B*, 2022, **317**, 121811.
- 107 P. Li, M. Wang, X. Duan, L. Zheng, X. Cheng, Y. Zhang, Y. Kuang, Y. Li, Q. Ma and Z. Feng, *Nat. Commun.*, 2019, **10**, 1711.
- 108 F. Song, W. Li, J. Yang, G. Han, T. Yan, X. Liu, Y. Rao, P. Liao, Z. Cao and Y. Sun, *ACS Energy Lett.*, 2019, **4**, 1594–1601.
- 109 L. Tao, Y. Shi, Y.-C. Huang, R. Chen, Y. Zhang, J. Huo, Y. Zou, G. Yu, J. Luo and C.-L. Dong, *Nano Energy*, 2018, **53**, 604–612.
- 110 Q. Dang, S. Tang, T. Liu, X. Li, X. Wang, W. Zhong, Y. Luo and J. Jiang, *J. Phys. Chem. Lett.*, 2021, **12**, 8355–8362.
- 111 K. Chu, Y.-p Liu, Y.-h Cheng and Q.-q Li, *J. Mater. Chem. A*, 2020, **8**, 5200–5208.
- 112 Y. Zhu, Z. He, Y. Choi, H. Chen, X. Li, B. Zhao, Y. Yu, H. Zhang, K. A. Stoerzinger and Z. Feng, *Nat. Commun.*, 2020, **11**, 4299.
- 113 A. Grimaud, O. Diaz-Morales, B. Han, W. T. Hong, Y.-L. Lee, L. Giordano, K. A. Stoerzinger, M. T. Koper and Y. Shao-Horn, *Nat. Chem.*, 2017, **9**, 457–465.
- 114 J. Hwang, R. R. Rao, L. Giordano, K. Akkiraju, X. R. Wang, E. J. Crumlin, H. Bluhm and Y. Shao-Horn, *Nat. Catal.*, 2021, **4**, 663–673.
- 115 L. Xu, Q. Jiang, Z. Xiao, X. Li, J. Huo, S. Wang and L. Dai, *Angew. Chem.*, 2016, **128**, 5363–5367.
- 116 H. Mistry, A. S. Varela, C. S. Bonifacio, I. Zegkinoglou, I. Sinev, Y.-W. Choi, K. Kisslinger, E. A. Stach, J. C. Yang and P. Strasser, *Nat. Commun.*, 2016, **7**, 12123.
- 117 R. Jia, Y. Wang, C. Wang, Y. Ling, Y. Yu and B. Zhang, *ACS Catal.*, 2020, **10**, 3533–3540.
- 118 J. Geng, S. Ji, H. Xu, C. Zhao, S. Zhang and H. Zhang, *Inorg. Chem. Front.*, 2021, **8**, 5209–5213.
- 119 N. Marcella, J. S. Lim, A. M. Plonka, G. Yan, C. J. Owen, J. E. van der Hoeven, A. C. Foucher, H. T. Ngan, S. B. Torrisi and N. S. Marinkovic, *Nat. Commun.*, 2022, **13**, 832.
- 120 F. Gao and D. W. Goodman, *Chem. Soc. Rev.*, 2012, **41**, 8009–8020.
- 121 Y. Liu, B. Deng, K. Li, H. Wang, Y. Sun and F. Dong, *J. Colloid Interface Sci.*, 2022, **614**, 405–414.
- 122 C. Lu, X. Lu, K. Yang, H. Song, S. Zhang and A. Li, *J. Mater. Sci.*, 2021, **56**, 7357–7371.
- 123 J. Li, H. Liu, F. Du, L. Liu, Y. Gu, C. Li, C. Guo and H. Wang, *Chem. Eng. J.*, 2023, **471**, 144488.
- 124 Y. Chen, Y. Zhao, Z. Zhao and Y. Liu, *Mater. Today Energy*, 2022, **29**, 101112.
- 125 Z. Tang, Z. Bai, X. Li, L. Ding, B. Zhang and X. Chang, *Processes*, 2022, **10**, 751.
- 126 V. Okatenko, A. Loiudice, M. A. Newton, D. C. Stoian, A. Blokhina, A. N. Chen, K. Rossi and R. Buonsanti, *J. Am. Chem. Soc.*, 2023, **145**, 5370–5383.
- 127 N. Sun, Y. Guo, L. Luo, X. Cai, S. Shen and J. Zhang, *Appl. Surf. Sci.*, 2023, **624**, 157118.
- 128 Z. Niu, S. Fan, X. Li, P. Wang, Z. Liu, J. Wang, C. Bai and D. Zhang, *Chem. Eng. J.*, 2022, **450**, 138343.
- 129 A. Wu, Y. Zhou, J. Lv, D. Zhang, Y. Peng, Q. Ye, P. Fu, W. Wang, X. Lin and S. Liu, *ACS Sustainable Chem. Eng.*, 2022, **10**, 14539–14548.
- 130 H. Liu, J. Li, F. Du, L. Yang, S. Huang, J. Gao, C. Li and C. Guo, *Green Energy Environ.*, 2023, **8**, 1619–1629.
- 131 W. He, J. Zhang, S. Dieckhöfer, S. Varhade, A. C. Brix, A. Lielpetere, S. Seisel, J. R. Junqueira and W. Schuhmann, *Nat. Commun.*, 2022, **13**, 1129.
- 132 W. Fu, Y. Du, J. Jing, C. Fu and M. Zhou, *Appl. Catal., B*, 2023, **324**, 122201.
- 133 X. Zheng, Y. Yan, X. Li, Y. Liu and Y. Yao, *J. Hazard. Mater.*, 2023, **446**, 130679.
- 134 F. Du, Z. Yao, J. Xiang, J. Li, C. Wang, C. Zhang, T. Hu, J. Liu, C. Li and C. Guo, *Appl. Surf. Sci.*, 2023, **608**, 155057.
- 135 N.-T. Suen, S.-F. Hung, Q. Quan, N. Zhang, Y.-J. Xu and H. M. Chen, *Chem. Soc. Rev.*, 2017, **46**, 337–365.
- 136 H.-H. Perkampus, *UV-VIS Spectroscopy and its Applications*, Springer Science & Business Media, 2013.
- 137 P. L. Searle, *Analyst*, 1984, **109**, 549–568.
- 138 C. D. Stalikas, A. C. Pappas, M. I. Karayannis and P. G. Veltsistas, *Microchim. Acta*, 2003, **142**, 43–48.
- 139 P. R. Haddad and P. E. Jackson, *Ion Chromatography*, Elsevier, 1990.
- 140 Y. Yao, L. Zhao, J. Dai, J. Wang, C. Fang, G. Zhan, Q. Zheng, W. Hou and L. Zhang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202208215.
- 141 J. Choi, B. H. Suryanto, D. Wang, H.-L. Du, R. Y. Hodgetts, F. M. Ferrero Vallana, D. R. MacFarlane and A. N. Simonov, *Nat. Commun.*, 2020, **11**, 1–10.
- 142 J. Long, S. Chen, Y. Zhang, C. Guo, X. Fu, D. Deng and J. Xiao, *Angew. Chem., Int. Ed.*, 2020, **59**, 9711–9718.
- 143 J. M. Rajput, D. S. Nandre and B. G. Pawar, *Int. J. Pharmaceut. Res. Anal.*, 2022, **7**, 53–62.
- 144 A. Bewick and K. Kunitatsu, *Surf. Sci.*, 1980, **101**, 131–138.
- 145 A. Bewick, K. Kunitatsu, B. Pons and J. Russell, *J. Electroanal. Chem. Interfacial Electrochem.*, 1984, **160**, 47–61.



- 146 A. Bewick, K. Kunimatsu, J. Robinson and J. Russell, *J. Electroanal. Chem. Interfacial Electrochem.*, 1981, **119**, 175–185.
- 147 J. Schnaidt, M. Heinen, Z. Jusys and R. J. Behm, *Electrochim. Acta*, 2013, **104**, 505–517.
- 148 P. Christensen, A. Hamnett and S. Weeks, *J. Electroanal. Chem. Interfacial Electrochem.*, 1988, **250**, 127–142.
- 149 H. Baltruschat, *J. Am. Soc. Mass Spectrom.*, 2004, **15**, 1693–1706.
- 150 A. Abd-El-Latif, C. Bondue, S. Ernst, M. Hegemann, J. Kaul, M. Khodayari, E. Mostafa, A. Stefanova and H. Baltruschat, *TrAC, Trends Anal. Chem.*, 2015, **70**, 4–13.
- 151 O. Wolter and J. Heitbaum, *Ber. Bunseng. Phys. Chem.*, 1984, **88**, 2–6.
- 152 Y. Yao, S. Zhu, H. Wang, H. Li and M. Shao, *Angew. Chem.*, 2020, **132**, 10565–10569.
- 153 M. Fleischmann, P. J. Hendra and A. J. McQuillan, *Chem. Phys. Lett.*, 1974, **26**, 163–166.
- 154 S. Schlücker, *Angew. Chem., Int. Ed.*, 2014, **53**, 4756–4795.
- 155 Y. Zhu, Y. Zhang, J. Li, B. Ren and Z. Tian, *Chinese J. Appl. Chem.*, 2018, **35**, 984.
- 156 C. S. Wondergem, T. Hartman and B. M. Weckhuysen, *ACS Catal.*, 2019, **9**, 10794–10802.
- 157 D. P. Butcher Jr and A. A. Gewirth, *Nano Energy*, 2016, **29**, 457–465.
- 158 E. Murray, P. Roche, M. Briet, B. Moore, A. Morrin, D. Diamond and B. Paull, *Talanta*, 2020, **216**, 120955.
- 159 M. F. Delley, E. M. Nichols and J. M. Mayer, *J. Am. Chem. Soc.*, 2021, **143**, 10778–10792.
- 160 M. A. Vuurman and I. E. Wachs, *J. Phys. Chem.*, 1992, **96**, 5008–5016.
- 161 H. Li, P. Wei, D. Gao and G. Wang, *Curr. Opin. Green Sustainable Chem.*, 2022, 100589.
- 162 I. E. Wachs, *Top. Catal.*, 1999, **8**, 57–63.
- 163 Y. Zhao, X. Chang, A. S. Malkani, X. Yang, L. Thompson, F. Jiao and B. Xu, *J. Am. Chem. Soc.*, 2020, **142**, 9735–9743.
- 164 N. Orlovskaya, D. Steinmetz, S. Yarmolenko, D. Pai, J. Sankar and J. Goodenough, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2005, **72**, 014122.
- 165 J. Evans, *X-Ray Absorption Spectroscopy for the Chemical and Materials Sciences*, John Wiley & Sons Ltd., 2017, pp. 1–8, DOI: [10.1002/9781118676165](https://doi.org/10.1002/9781118676165).
- 166 H. Zhong, M. Wang, M. Ghorbani-Asl, J. Zhang, K. H. Ly, Z. Liao, G. Chen, Y. Wei, B. P. Biswal and E. Zschech, *J. Am. Chem. Soc.*, 2021, **143**, 19992–20000.
- 167 X. Zou, J. Xie, C. Wang, G. Jiang, K. Tang and C. Chen, *Chin. Chem. Lett.*, 2023, **34**, 107908.
- 168 C. Glass and J. Silverstein, *Water Res.*, 1999, **33**, 223–229.
- 169 X. Zhao, X. Jia, H. Zhang, X. Zhou, X. Chen, H. Wang, X. Hu, J. Xu, Y. Zhou and H. Zhang, *J. Hazard. Mater.*, 2022, **434**, 128909.
- 170 X. Zhao, X. Jia, Y. He, H. Zhang, X. Zhou, H. Zhang, S. Zhang, Y. Dong, X. Hu and A. V. Kuklin, *Appl. Mater. Today*, 2021, **25**, 101206.
- 171 Z. Ma, M. Klimpel, S. Budnyk, A. Rokicińska, P. Kustrowski, R. Dronskowski, A. P. Mathew, T. Budnyak and A. Slabon, *ACS Sustainable Chem. Eng.*, 2021, **9**, 3658–3667.
- 172 X. Wang, X. Wu, W. Ma, X. Zhou, S. Zhang, D. Huang, L. R. Winter, J.-H. Kim and M. Elimelech, *Proc. Natl. Acad. Sci. U. S. A.*, 2023, **120**, e2217703120.
- 173 G. Jiang, M. Peng, L. Hu, J. Ouyang, X. Lv, Z. Yang, X. Liang, Y. Liu and H. Liu, *Chem. Eng. J.*, 2022, **435**, 134853.
- 174 Y. Zeng, C. Priest, G. Wang and G. Wu, *Small Methods*, 2020, **4**, 2000672.
- 175 Z. Xu, L. Wan, Y. Liao, M. Pang, Q. Xu, P. Wang and B. Wang, *Nat. Commun.*, 2023, **14**, 1619.
- 176 W. Zheng, L. Zhu, Z. Yan, Z. Lin, Z. Lei, Y. Zhang, H. Xu, Z. Dang, C. Wei and C. Feng, *Environ. Sci. Technol.*, 2021, **55**, 13231–13243.
- 177 A.-J. Wang, H.-C. Wang, H.-Y. Cheng, B. Liang, W.-Z. Liu, J.-L. Han, B. Zhang and S.-S. Wang, *Environ. Sci. Ecotechnol.*, 2020, **3**, 100050.
- 178 Z. Pan, F. Khalid, A. Tahir, O. C. Esan, J. Zhu, R. Chen and L. An, *Fundam. Res.*, 2022, **2**, 757–763.
- 179 J. M. McEnaney, S. J. Blair, A. C. Nielander, J. A. Schwalbe, D. M. Koshy, M. Cargnello and T. F. Jaramillo, *ACS Sustainable Chem. Eng.*, 2020, **8**, 2672–2681.
- 180 J. Gao, N. Shi, X. Guo, Y. Li, X. Bi, Y. Qi, J. Guan and B. Jiang, *Environ. Sci. Technol.*, 2021, **55**, 10684–10694.
- 181 D. Vineyard, A. Hicks, K. Karthikeyan and P. Barak, *J. Cleaner Prod.*, 2020, **262**, 121145.

