






Cite this: *Sustainable Energy Fuels*,  
2025, 9, 5278

# Neutron imaging to study the influence of flow fields and porous electrodes on concentration distributions in redox flow cells

Maxime van der Heijden, \*<sup>ab</sup> Rémy Richard Jacquemond, <sup>a</sup> Emre Burak Boz, <sup>ac</sup>  
Pierre Boillat <sup>de</sup> and Antoni Forner-Cuenca <sup>ac</sup>

Understanding reactive mass transport in redox flow reactors is key to improving performance, yet conventional characterization techniques often rely on cell-averaged metrics and fail to resolve local transport phenomena. In this study, we employ *operando* neutron radiography to visualize concentration distributions in redox flow cells with non-aqueous electrolytes, leveraging the high attenuation of hydrogen-containing organic molecules and boron-containing supporting ions. Symmetric flow cell experiments were conducted with three electrode types (paper, cloth, and a hierarchical porous electrode fabricated by non-solvent induced phase separation), and two flow field designs (parallel and interdigitated). We find that for kinetically facile electrolytes with low ionic conductivity and with parallel flow fields, electrodes with large pores in the through-plane direction (*i.e.*, carbon cloth) augment the current output. Additionally, interdigitated flow fields sustain higher currents than parallel flow fields at a fixed potential and flow rate due to enhanced convective transport. Despite significant differences in macroscopic performance among the studied materials, the concentration profiles within the cell showed only minor variations within the studied operating conditions and imaging configuration. The cloth electrode and interdigitated flow field exhibited slightly more uniform concentration profiles across the electrode thickness compared to the paper electrode with the parallel flow field. In contrast, the phase-separation electrode displayed more steep concentration profiles and a stronger dependency on polarity reversal. Neutron radiography further uncovered critical secondary effects, including salt precipitation and flow field underutilization. These findings highlight the potential of *operando* imaging to inform the design and operation of electrochemical reactors for a range of technologies.

Received 16th June 2025  
Accepted 1st August 2025DOI: 10.1039/d5se00844a  
rsc.li/sustainable-energy

## 1 Introduction

Redox flow batteries (RFBs) are rechargeable electrochemical systems that are promising for large-scale stationary energy storage due to their design flexibility which enables independent scaling of power and energy, simple manufacturing, and system adaptability (*i.e.*, different electrolytes and operating conditions).<sup>1–5</sup> In RFBs, electrolytes containing dissolved or suspended redox active species are stored in external tanks and

pumped through the electrochemical reactor where the active species undergo redox reactions to charge and discharge the battery. The electrochemical stack comprises current collectors with flow fields, porous electrodes, and membranes, which together determine the power output of the system. Among various technical challenges (*e.g.*, performance, lifetime, power losses (overpotentials)) in the battery limit the system efficiency and lead to increased capital costs.<sup>6</sup> Enhancing power density in electrochemical cells requires optimizing reactor design, material selection, and operating conditions to improve reactive mass transport.<sup>5</sup> The porous electrodes control the electrolyte distribution, provide active surfaces for reactions, cushion mechanical compression, and facilitate mass, charge, and heat transport,<sup>7,8</sup> whereas flow fields distribute the electrolyte to the porous electrodes, affecting pressure drop and electrode utilization.<sup>8–11</sup> Understanding the interplay between mass transport and reactions is crucial for designing better reactors and materials. To this end, there is a growing interest in investigating the performance of conventional porous electrodes under specific reactor designs and conditions<sup>3,10,12–19</sup> as

<sup>a</sup>Electrochemical Materials and Systems, Department of Chemical Engineering and Chemistry, Eindhoven University of Technology, P.O. Box 513, 5600 MB Eindhoven, The Netherlands. E-mail: r.r.jacquemond@tue.nl; e.b.boz@tue.nl; a.forner.cuenca@tue.nl

<sup>b</sup>Department of Chemical Engineering, University of Waterloo, Waterloo, ON, Canada. E-mail: maxime.vanderheijden@uwaterloo.ca

<sup>c</sup>Eindhoven Institute for Renewable Energy Systems, Eindhoven University of Technology, P.O. Box 513, 5600 MB Eindhoven, The Netherlands

<sup>d</sup>Electrochemistry Laboratory, Paul Scherrer Institut, Forschungsstrasse 111, Villigen PSI, CH-5232, Switzerland. E-mail: pierre.boillat@psi.ch


<sup>e</sup>Laboratory for Neutron Scattering and Imaging, Paul Scherrer Institut, Forschungsstrasse 111, Villigen PSI, CH-5232, Switzerland



the flow field design, electrolyte chemistry, and operating conditions significantly impact the electrode performance.<sup>3,9</sup>

Conventional techniques for evaluating electrochemical cell performance rely on electrochemical diagnostic tools, *e.g.*, polarization curves and electrochemical impedance spectroscopy, along with *ex situ* characterization methods such as scanning electron microscopy and X-ray photoelectron spectroscopy.<sup>8</sup> However, local *operando* metrics, such as concentration distributions, are complex to resolve, which are essential for correlating material and reactor components to battery performance. Combining *operando* imaging diagnostics (*e.g.*, X-

ray tomography,<sup>20–23</sup> fluorescence imaging,<sup>24</sup> (nuclear) magnetic resonance imaging,<sup>25–28</sup> and neutron imaging<sup>29–33</sup>), with conventional electrochemical tools is a promising approach. Neutron imaging is particularly useful as it enables reactor-level, long-duration, and non-invasive imaging.<sup>29</sup> As shown in our previous work,<sup>30</sup> the relatively high attenuation of hydrogen and boron<sup>34,35</sup> makes this technique suitable to study non-aqueous RFBs (NAqRFBs) with organic redox molecules. Due to the low attenuation of cell housing, neutron imaging enables the study of various reactor components by contrasting redox-active molecules, supporting ions, solvents, and gases, while

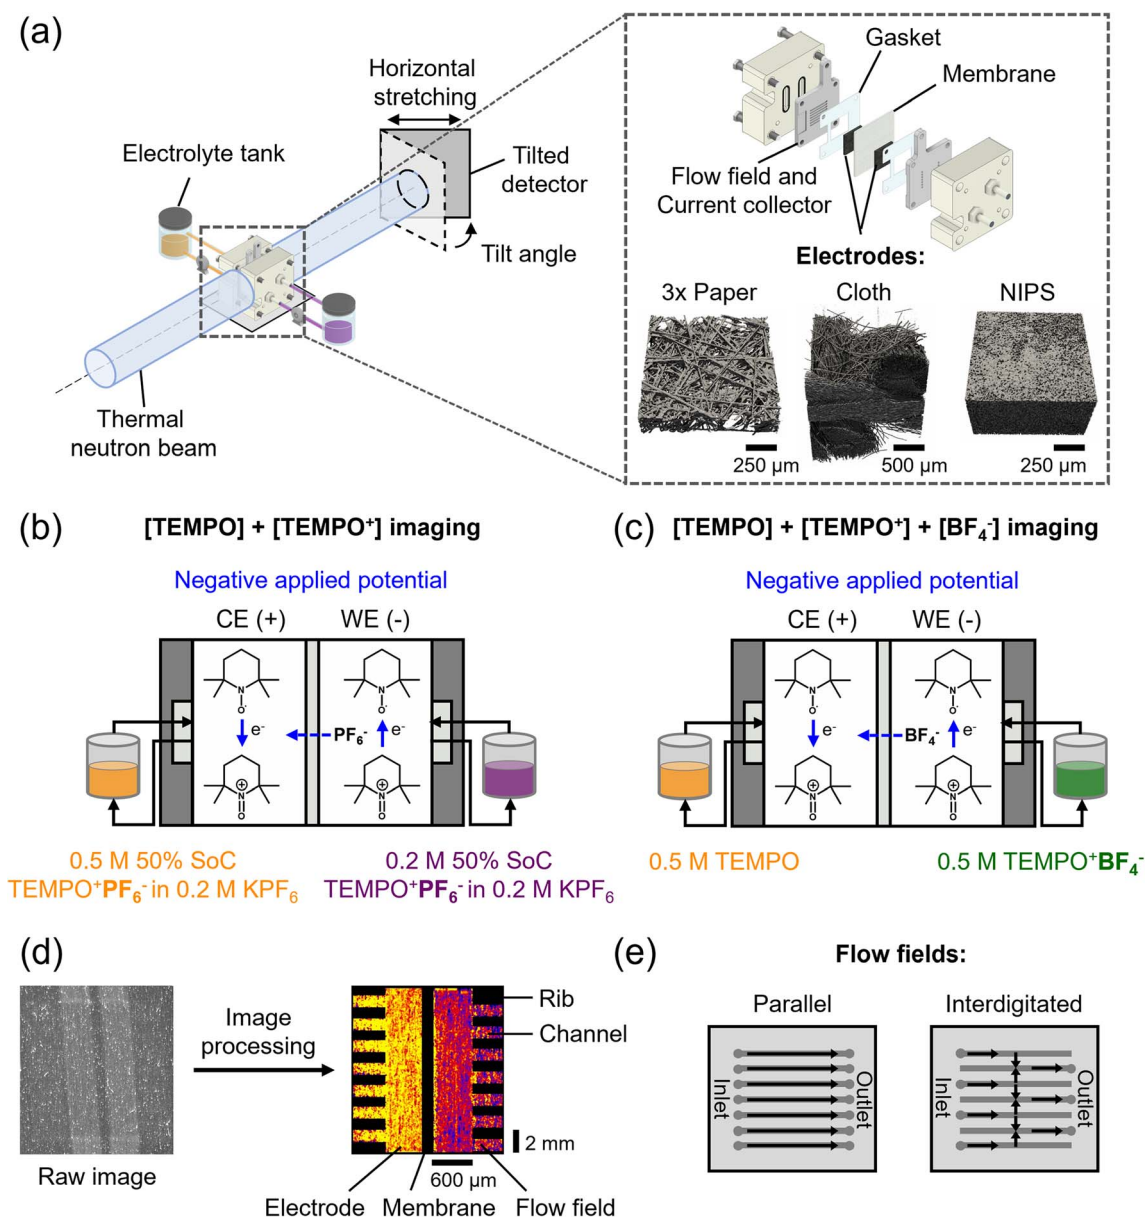

**Fig. 1** Schematic representations of (a) the neutron imaging set-up for cumulative concentration profiles of active species and supporting ions, together with the flow cell design, cell components, and the X-ray tomographic images of the electrode types: three stacked papers, a cloth, and an in-house manufactured NIPS electrode; (b) and (c) the non-aqueous cell design with chemical structures of the active species (TEMPO and TEMPO<sup>+</sup>), shown for a negative applied potential, and the different electrolyte tank compositions: (b) 0.5 M [TEMPO] + [TEMPO<sup>+</sup>PF<sub>6</sub><sup>-</sup>] at 50% state-of-charge in 0.2 M KPF<sub>6</sub> at the counter electrode (CE) and 0.2 M [TEMPO] + [TEMPO<sup>+</sup>PF<sub>6</sub><sup>-</sup>] at 50% state-of-charge in 0.2 M KPF<sub>6</sub> at the working electrode (WE), and (c) 0.5 M TEMPO at the CE and 0.5 M TEMPO<sup>+</sup>BF<sub>4</sub><sup>-</sup> at the WE; (d) simplified image processing steps from raw to processed image showing the flow fields, electrodes, and porous separator; (e) flow field types used: parallel and interdigitated.





### 2.3 Neutron radiography

Neutron radiography experiments were conducted at the NEUTRA beamline in the Spallation Neutron Source facility of the Paul Scherrer Institute, Switzerland. The NEUTRA beamline operates with thermal neutrons emitted from a lead spallation target upon interaction with a proton beam (590 MeV energy, 1.5 mA proton current) and moderated by heavy water to reach thermal velocities (25 meV).<sup>39</sup> The beamline was equipped with an in-plane imaging set-up with a tilted charge-coupled device camera detector (CCD, Andor, 30 s exposure time) to produce a stretched image in the horizontal transverse direction with respect to the incident beam (Fig. 1a), allowing higher spatial resolution across the flow field-electrode-separator domain.<sup>40</sup> This resulted in a pixel size of 6  $\mu\text{m}$ , translating to an effective resolution of 20  $\mu\text{m}$  considering beam divergence and detector blurring. Attenuated neutrons were captured by a scintillator screen (10  $\mu\text{m}$  thick,  $\text{Gd}_2\text{O}_2\text{S}:\text{Tb}$ ), converted to visible light, and confined by the CCD detector. The imaging configuration allows us to resolve the concentration distribution locally through the electrode thickness (Fig. 1d) and provides deeper insights into coupled mass transport phenomena (convection, diffusion, migration) unattainable with conventional characterization methods.

### 2.4 Calibration experiments

*Ex situ* cuvette calibration measurements were performed to obtain the attenuation coefficients of various electrolyte solutions to quantify the total concentration in the electrochemical cells. The attenuation coefficients, *i.e.*, the attenuation of the neutron beam by the sample, were obtained with the Lambert-Beer law:<sup>41</sup>

$$T = e^{-\sigma_i n_i \delta} \quad (1)$$

where  $T$  is the transmitted intensity [–] corrected for the attenuation of an empty cuvette,  $\sigma_i$  the conventional microscopic cross-section [ $\text{m}^2$ ],  $n_i$  the number density of species  $i$  [ $\text{m}^{-3}$ ] which is a function of the concentration of species  $i$  ( $C_i$ ) [ $\text{mol m}^{-3}$ ] and Avogadro's number [ $\text{mol}^{-1}$ ] ( $N_A$ ,  $6.02 \times 10^{23} \text{ mol}^{-1}$ ) by  $C_i = n_i/N_A$ , and  $\delta$  the sample thickness [ $\text{m}$ ] which was 1 cm for the cuvettes and  $\delta = L_e \varepsilon_e$  for the flow cell experiments, with  $L_e$  being the electrode width (17 mm) [ $\text{m}$ ] and  $\varepsilon_e$  the electrode porosity at the applied compression [–]. The cuvette calibration measurements were performed to obtain the microscopic cross-sections for solutions of  $\text{CD}_3\text{CN}$  (solvent reference), 0.2 M  $\text{KPF}_6$  (supporting electrolyte), and solutions of varying molarities (0.1, 0.2, 0.3, 0.4, and 0.5 M) of TEMPO,  $\text{TEMPO}^+\text{PF}_6^-$ , and  $\text{TEMPO}^+\text{BF}_4^-$  to verify the linearity between the concentration and neutron attenuation, all dissolved in  $\text{CD}_3\text{CN}$ . The calibration experiments were extensively discussed in our previous work,<sup>30</sup> showing similar macroscopic cross-sections for TEMPO and  $\text{TEMPO}^+\text{PF}_6^-$  in  $\text{CD}_3\text{CN}$ ,  $\text{KPF}_6$  in  $\text{CD}_3\text{CN}$  has similar neutron attenuation to  $\text{CD}_3\text{CN}$ , and  $\text{TEMPO}^+\text{BF}_4^-$  has roughly double the macroscopic cross-section of TEMPO.

### 2.5 Flow cell configuration

The flow cell experiments were performed using a laboratory-scale system,<sup>3,42,43</sup> with the cell mounted on a robotized platform 1–3 mm in front of the neutron detector. The cell was slightly modified (grooved flow fields and gaskets around the active area, see Fig. 1a) to enhance sensitivity by minimizing cell part attenuation without impacting electrolyte transport. Electrolyte solutions were pumped through the cell using a Masterflex L/S® peristaltic pump with an Easy-Load® II pump head and LS-14 tubing, connected to two 20 mL reservoirs. Custom-made flow cells featured machined polypropylene diffusers (McMaster-Carr) and graphite current collectors (G347B graphite, 3.18 mm thick, MWI, Inc.), milled with parallel (seven  $16 \times 1 \times 0.5 \text{ mm}^3$  channels parallel to the electrolyte flow) or interdigitated flow field designs (seven  $16 \times 1 \times 0.5 \text{ mm}^3$  channels parallel to the electrolyte flow, of which four inlet- and three outlet channels) (Fig. 1e). Electrodes (2.55  $\text{cm}^2$  geometric area) were confined within incompressible polytetrafluorethylene gaskets (ERIKS, thicknesses of 210  $\mu\text{m}$  and 110  $\mu\text{m}$  were used). A Daramic 175 porous separator (SLI Flatsheet Membrane, 175  $\mu\text{m}$ ) was used to separate the half-cells and the cell was tightened to 2 Nm with a torque-controlled wrench.

To compare the flow cell performance between the different electrodes, the electrolyte flow rate was controlled. Evaluated flow rates were 15.3 and 5.1  $\text{mL min}^{-1}$  for the paper electrode, 15.3, 5.1, 45.9, and 1.7  $\text{mL min}^{-1}$  for the cloth electrode, and 12.8 and 4.5  $\text{mL min}^{-1}$  for the NIPS electrode, performed in descending order to remove residual gas bubbles and enhance electrode wetting. Furthermore, two flow field designs, PFF and IDFF, were investigated with the paper electrode at constant flow rates (15.3 and 5.1  $\text{mL min}^{-1}$ ). The electrolyte velocity can be obtained with eqn (2) for the PFF and eqn (3) for the IDFF, shown for both the electrolyte velocity in the channel and in the electrode. However, calculating the velocity through the electrode with a PFF is challenging, and often a negligible electrolyte velocity is assumed.<sup>12,15</sup>

$$v_{\text{PFF, ch}} = \frac{Q}{N_{\text{ch}} W_{\text{ch}} D_{\text{ch}}}, v_{\text{PFF, e}} \approx 0 \quad (2)$$

$$v_{\text{IDFF, ch}} = \frac{Q}{N_{\text{ch, in}} W_{\text{ch}} D_{\text{ch}}}, v_{\text{IDFF, e}} = \frac{Q}{(N_{\text{ch}} - 1) L_{\text{ch}} L_{\text{e}}} \quad (3)$$

with  $v$  being the electrolyte velocity [ $\text{m s}^{-1}$ ] with the PFF or IDFF in the flow channel or the electrode,  $Q$  the electrolyte flow rate [ $\text{m}^3 \text{ s}^{-1}$ ],  $N_{\text{ch}}$  the total number of channels in the flow field configuration (7 channels) [–],  $N_{\text{ch, in}}$  the number of inlet channels (4 channels for the IDFF) [–],  $W_{\text{ch}}$  the channel width ( $1 \times 10^{-3} \text{ m}$ ) [ $\text{m}$ ],  $D_{\text{ch}}$  the channel depth ( $5 \times 10^{-4} \text{ m}$ ) [ $\text{m}$ ],  $L_{\text{ch}}$  the channel length ( $1.6 \times 10^{-2} \text{ m}$ ) [ $\text{m}$ ], and  $L_{\text{e}}$  the compressed electrode thickness ( $6.3 \times 10^{-4} \text{ m}$  or  $5.3 \times 10^{-4} \text{ m}$ ) [ $\text{m}$ ].

### 2.6 Electrochemical performance

For the electrochemical cells, the procedure started with measuring the open circuit voltage (OCV) to monitor species diffusion between the half-cells for 20 min for the  $\text{KPF}_6$  supporting salt experiments or for 1 hour for the  $\text{BF}_4^-$  supporting



ion experiments. OCV experiments were performed at 15.1 mL min<sup>-1</sup>, except for the NIPS electrode (12.8 mL min<sup>-1</sup>). The electrochemical sequence involved applying -0.3 V, +0.3 V, -0.6 V, and +0.6 V using a BioLogic VSP-3e potentiostat, with each step lasting 20 min at each flow rate (Section 2.5), resulting in an electrochemical protocol of 180–220 min for the paper electrode for both flow fields (Fig. S6 and S9). The NIPS electrode followed the same protocol (Fig. S1c), but due to a beam shutdown, some images were missing (-0.3 V and +0.3 V at 4.5 mL min<sup>-1</sup> for the BF<sub>4</sub><sup>-</sup> experiment at ~90 min, the -0.6 V and +0.6 V sequences at both flow rates were repeated, Fig. S3c). There was also a beam shutdown for the IDFF, resulting in a time jump of 40 min (KPF<sub>6</sub> experiment at 100–140 min, Fig. S6b). The cloth electrode (Fig. S1b and S3b) was investigated at two additional flow rates (at -0.6 V and +0.6 V for 20 min), resulting in a sequence of 260–300 min. Neutron radiographs were collected throughout. Both supporting salt (KPF<sub>6</sub>) and supporting ion (BF<sub>4</sub><sup>-</sup>) experiments were performed on the same cell, with a rinsing step in between using 0.5 M TEMPO in CD<sub>3</sub>CN, except for the paper-PFF configuration.

## 2.7 Image processing

The image processing steps to obtain the final concentration distribution color maps (Fig. 1d) were performed using a Jupyter Notebook script. Transmission data was corrected for detector background effects, beam variations, changes in the sample position, interactions of the beam with other cell components, and camera noise, in a subtractive manner. Five image sets were obtained: raw images, black body, open beam, dark current, and reference images. The raw images of the cell with the electrolyte solution (low attenuating salt KPF<sub>6</sub> or highly attenuating supporting ion BF<sub>4</sub><sup>-</sup>) were processed as follows:

- (1) *Dark current correction*: eliminates electronic bias within the camera circuitry.
- (2) *Filtering*: a white spot filter corrects gamma radiation effects and a Gaussian filter reduces statistical noise.
- (3) *Open beam correction*: corrects spatial variations in beam intensity.
- (4) *Registration*: accounts for cell movements due to relaxation or thermal dilation.
- (5) *Intensity correction*: adjusts for beam intensity variations.
- (6) *Scattered background correction*: corrects for neutrons scattered by the detector and cell.
- (7) *Referencing*: obtains the transmission values of the species of interest.
- (8) *Image rotation*: aligns the cells horizontally.
- (9) *Cell mask application*: shows the region of interest (flow fields and electrodes, Fig. 1d). A mask is applied over the porous separator because the active species concentration cannot be accurately determined due to the separator's low thickness and high neutron attenuation.
- (10) *Concentration calculation*: uses Lambert-Beer law (eqn (1)) to translate neutron transmission to concentration. With a "concentration factor" ( $-\sigma_i n_i \delta$ ) of -0.891 L mol<sup>-1</sup> for the paper and NIPS electrodes, and -0.686 L mol<sup>-1</sup> for the cloth electrode (lower porosity).

An extensive description of the image processing steps can be found in our previous work.<sup>30</sup>

## 3 Results and discussion

### 3.1 Influence of the electrode structure

**3.1.1. Transport of the active species.** As described in our previous work,<sup>30</sup> imaging of the active species TEMPO and TEMPO<sup>+</sup> can be achieved using the low attenuating supporting salt KPF<sub>6</sub>. The movement of active species due to concentration gradients and voltage bias can be visualized by tracking their concentration distribution through the reactor owing to the large neutron attenuation of hydrogen-containing TEMPO species. Accordingly, electrolyte tanks with 50% SoC TEMPO and TEMPO<sup>+</sup> with 0.5 M on the counter electrode (CE) side and 0.2 M on the working electrode (WE) side were used, both with 0.2 M KPF<sub>6</sub> for ionic conductivity and minimal neutron attenuation (Fig. 1b). Fig. 2 shows electrochemical data and concentration profiles over the electrode thickness from the CE to WE for the three electrode types at OCV, -0.6 V, and +0.6 V at 5 mL min<sup>-1</sup>. The images and profiles were averaged over 20 min for each applied potential and represent a pixel average (over the electrode length and width) in the direction of the neutron beam. Higher flow rate and lower potential profiles are shown in Section S1.1. In generating the concentration distribution profiles (Fig. 2c), only the porous electrode region was considered in the averaging process. Flow fields, including rib areas (porosity = 0) and flow channels (porosity = 1), were excluded to avoid skewing the results. The flow field domain typically exhibits lower average neutron attenuation which dilutes the concentration signal. While visually retained in the images for contextual awareness, they do not contribute to the plotted averages. Fig. 2c includes a reference box to indicate the specific region analyzed in the 1D concentration plots, which was applied to all concentration profiles plotted in the main article as well as the SI.

The cells were first analyzed at OCV to study mass transport without applied potential. At OCV, the cumulative TEMPO and TEMPO<sup>+</sup> concentrations (*i.e.*, [TEMPO] + [TEMPO<sup>+</sup>]) in the electrodes remained fairly constant and uniform over time and thickness in each half-cell (Fig. 2b), indicating the 20 min timeframe was too short for species diffusion through the porous separator to balance the concentration gradient.<sup>44</sup> After the OCV period, alternating negative and positive voltage biases were applied, and the current output was recorded (Fig. 2a). A negative potential at the WE caused species movement due to redox reactions and the electric field,<sup>45</sup> increasing species concentration in the WE and decreasing it in the CE. TEMPO was oxidized to TEMPO<sup>+</sup> at the CE and migrated towards the WE, accompanied by diffusion due to the concentration gradient.<sup>45</sup> Reversing the potential showed the opposite behavior, with concentration profiles converging toward the initial OCV values.

Despite the different microstructures of the paper and NIPS electrodes, their macroscopic electrochemical response is similar, both delivering a constant current output of approximately ±100 mA at an applied potential of ±0.6 V. Although the NIPS electrode has a higher electrochemically active surface





Fig. 2 *Operando* neutron imaging of the active species transport with the low attenuating  $\text{KPF}_6$  supporting salt for three electrode types: paper, cloth, and an in-house manufactured NIPS electrode, at an inlet flow rate of  $5 \text{ mL min}^{-1}$  and evaluated at OCV,  $-0.6 \text{ V}$ , and  $+0.6 \text{ V}$ . (a) The potential applied and current output of the electrochemical cells. (b) The averaged concentration profiles over time in the counter electrode (CE) and the working electrode (WE). (c) The cumulative active species ( $\text{TEMPO}$  and  $\text{TEMPO}^+$ ) concentration profiles over the electrode thickness with the averaged snapshots of the cell after image processing, with on the counter electrode  $0.5 \text{ M } [\text{TEMPO}] + [\text{TEMPO}^+\text{PF}_6^-]$  at 50% state-of-charge in  $0.2 \text{ M } \text{KPF}_6$  and at the working electrode  $0.2 \text{ M } [\text{TEMPO}] + [\text{TEMPO}^+\text{PF}_6^-]$  at 50% state-of-charge in  $0.2 \text{ M } \text{KPF}_6$ . The white dashed box in the OCV image for the paper electrode shows the area of the images that are plotted in the concentration profiles, *i.e.*, the porous electrode, excluding the flow field.

area ( $2.9 \text{ m}^2 \text{ g}^{-1}$ )<sup>36</sup> compared to the paper electrode ( $0.50 \text{ m}^2 \text{ g}^{-1}$ ),<sup>3</sup> the current output is similar because of the facile kinetics and low ionic conductivity of the electrolyte,<sup>19</sup> as well as the porosity gradient and low permeability across the NIPS electrode thickness.<sup>10,19,36,46</sup> The electrochemical performance of the

cloth electrode, however, is considerably different, with a current output 2.5 times higher (average of  $\pm 240 \text{ mA}$  over 20 min at  $\pm 0.6 \text{ V}$ ) than the paper and NIPS electrodes. The current decreases over time due to the high species conversion, which affects the SoC in the cell.<sup>8,44</sup> The superior performance of



the cloth electrode is attributed to its weave structure, which provides a bimodal PSD (pore diameters centered at *ca.* 20  $\mu\text{m}$  and 100  $\mu\text{m}$  with pores spanning 5–500  $\mu\text{m}^3$ ) with large voids in the through-plane direction. This structure results in high through-plane permeability, low tortuosity (1.15–1.35), and low apparent Forchheimer coefficient ( $1.2 \times 10^3 \text{ m}^{-1}$ ),<sup>13</sup> which is beneficial in combination with low convection due to the PFF and low flow rate, and low ionic conductivity of the electrolyte.<sup>46</sup>

In contrast, the paper and NIPS electrodes feature differences in the concentration distributions (Fig. S2b). The NIPS electrode shows significant changes in the concentration profiles with polarity reversal, featuring a pronounced slope in the electrode thickness in the WE, from a concentration close to the tank concentration at the flow field to a higher concentration near the separator. These findings are a result of the migration of TEMPO<sup>+</sup> species in response to the electric field<sup>30</sup> and the diffusion of active species from the concentrated to the dilute side,<sup>45</sup> influenced by the distinct electrode microstructure and amplified by low convection (PFF).<sup>15</sup> The NIPS electrode contains smaller pores ( $\sim 1\text{--}5 \mu\text{m}$ ) with a gradient in the electrode thickness with smaller pores facing the separator for high electrochemical activity,<sup>10,19,37</sup> leading to higher tortuosity, lower apparent permeability ( $1.0 \times 10^{-11} \text{ m}^2$  for the NIPS electrode<sup>13</sup> vs.  $7.4 \times 10^{-11} \text{ m}^2$  for the paper electrode<sup>3</sup>), and lower effective diffusivity compared to the paper electrode, which has an average pore size of 63  $\mu\text{m}^3$ . Consequently, we hypothesize that the NIPS electrode studied here suffers from lower convective mass transport, especially at low flow rates, causing steep concentration profiles. Conversely, the cloth electrode features more uniform profiles in the electrode thickness (Fig. S2a) due to higher convective mass transport. Moreover, the concentration changes in the CE and WE are smaller over time for all flow rates and applied potentials (Fig. S1b). The large through-plane void segments of the cloth electrode enhance diffusion and convection, resulting in smaller concentration differences across the electrode thickness and higher current output due to redox reactions occurring throughout a greater electrode volume.<sup>46</sup>

The concentration variations between the cloth and paper electrodes are minor compared to the significant differences in macroscopic electrochemical output. Whereas for the NIPS electrode, the macroscopic trends are similar to the paper electrode, despite differences in their concentration distribution through the cell. Since cumulative concentration profiles of [TEMPO] + [TEMPO<sup>+</sup>] are studied, distinguishing reactions from migration and diffusion remains challenging. Future research on alternative redox probes and computational models could help bridge this gap. Combining electrochemical performance with *operando* neutron radiography correlates the current output to concentration distributions in the cell, revealing that a bimodal PSD with large through-plane voids and high effective diffusivity is beneficial for PFF configurations with a TEMPO-based electrolyte. We then apply neutron imaging with a highly attenuating supporting ion (BF<sub>4</sub><sup>−</sup>) and different electrolyte compositions to further investigate the transport of counter-ions and the influence of diffusion, convection, and migration on concentration profiles.

**3.1.2 Transport of the counter-ion.** In this section, we discuss the cumulative imaging of active species and supporting ions using the high attenuation of BF<sub>4</sub><sup>−</sup> (*i.e.*, [TEMPO] + [TEMPO<sup>+</sup>] + [BF<sub>4</sub><sup>−</sup>]). With an electrolyte configuration of 0.5 M TEMPO at the CE and 0.5 M TEMPO<sup>+</sup>BF<sub>4</sub><sup>−</sup> at the WE (Fig. 1c), the movement of the counter-ion BF<sub>4</sub><sup>−</sup> can be studied. In our previous work,<sup>30</sup> this configuration enabled tracking of counter-ion movement through an anion exchange membrane. However, in this work, a porous separator was used, which has no charge selectivity, permitting the transport of all species between the half-cells, enabling the study of cumulative active species and supporting ion diffusion and migration over time. The *operando* electrochemical data and concentration profiles for the three electrodes at OCV, −0.6 V, and +0.6 V for a flow rate of 5 mL min<sup>−1</sup> are shown in Fig. 3. The electrochemical sequence and concentration profiles at higher flow rates and lower potentials are shown in Section S1.2, along with capacity data.

At the start of the experiments at open circuit, the OCV is not zero due to the potential difference between the half-cells caused by the initial electrolyte compositions. Over time, the OCV decreases because of electrolyte mixing between the compartments caused by species diffusion through the separator,<sup>44</sup> but the time frame is not long enough to balance the concentrations in both half-cells. When a negative potential is applied, TEMPO is oxidized to TEMPO<sup>+</sup> at the CE and migrates towards the WE, creating a concentration gradient. TEMPO then diffuses towards the CE through the porous separator. BF<sub>4</sub><sup>−</sup> migrates towards the CE to support the TEMPO oxidation reaction, resulting in an overall increase in attenuation in the CE and a decrease in the WE.<sup>45</sup> When a positive potential is applied, the opposite behavior is observed, and the concentration profiles converge toward the initial OCV values.

Before analyzing the differences between the three electrodes, it is important to note that the CE in the configuration with the paper electrode cannot be analyzed quantitatively due to significant salt precipitation, affecting the neutron attenuation of the electrolyte (highlighted in Fig. 3c). Salt precipitation in the paper electrode configuration was confirmed by the absence of time-dependent changes in local concentration signals, even under polarity and flow rate reversal, indicating solid-phase formation rather than mobile dissolved species concentration. The salt precipitation resulted from not rinsing the cells between the KPF<sub>6</sub> supporting salt and BF<sub>4</sub><sup>−</sup> counter ion experiments, as BF<sub>4</sub><sup>−</sup> ions precipitate when in contact with residual K<sup>+</sup> ions due to the low solubility of KBF<sub>4</sub> in acetonitrile.<sup>47</sup> As salt precipitation adversely affects neutron attenuation and battery performance by obstructing ion transport, diminishing available surface area, and ultimately shortened battery lifespan, subsequent experiments incorporated a rinsing step using 0.5 M TEMPO solution between experiments with different electrolytes (Section 2.6). Future salt precipitation mitigation strategies could include the use of highly soluble salt pairs, implementation of intermediate electrolyte flushing cycles between different chemistries, and surface modifications of electrodes to minimize nucleation and growth of precipitates.





Fig. 3 *Operando* neutron imaging of the active species transport with the attenuating  $\text{BF}_4^-$  supporting ion for three electrode types: paper, cloth, and an in-house manufactured NIPS electrode, at an inlet flow rate of  $5 \text{ mL min}^{-1}$  and evaluated at OCV,  $-0.6 \text{ V}$ , and  $+0.6 \text{ V}$ . (a) The potential applied and current output of the electrochemical cells. (b) The averaged concentration profiles over time in the counter electrode (CE) and the working electrode (WE). (c) The cumulative active species ( $\text{TEMPO}$  and  $\text{TEMPO}^+$ ) and  $\text{BF}_4^-$  supporting ion concentration profiles over the electrode thickness with the averaged snapshots of the cell after image processing, with on the counter electrode  $0.5 \text{ M TEMPO}$  and at the working electrode  $0.5 \text{ M TEMPO}^+\text{BF}_4^-$ . Salt precipitation in the cell is highlighted in the snapshots.

The electrochemical output for the paper and NIPS electrodes is again similar ( $\sim \pm 75 \text{ mA}$  at  $\pm 0.6 \text{ V}$ ), supported by the capacity curves (Fig. S5) showing  $\sim 10\%$  conversion at  $5 \text{ mL min}^{-1}$  and  $-0.6 \text{ V}$  in 20 min. The cloth electrode, however, exhibits higher current ( $-244 \text{ mA}$  at  $-0.6 \text{ V}$ ) and capacity with a 35% conversion rate, resulting in a drop in current over time at a constant applied potential (Fig. 3a).<sup>44</sup> Additionally, the

current output for the cloth electrode is similar for both  $\text{KPF}_6$  and  $\text{BF}_4^-$  experiments, whereas it is lower for the  $\text{BF}_4^-$  experiment with the paper and NIPS electrodes ( $\sim \pm 75 \text{ mA}$  vs. at  $\pm 100 \text{ mA}$   $\pm 0.6 \text{ V}$ ). This difference is due to the lower ionic conductivity of the electrolytes in the  $\text{BF}_4^-$  ion experiments, as no supporting salt was added. The hydraulic conductance of the paper and NIPS electrodes limit their performance, making



them more sensitive to the electrolyte conductivity, while the cloth electrode's higher hydraulic conductance makes it less sensitive to these changes.<sup>46</sup>

Nuanced differences in the concentration distributions are observed, with the NIPS electrode showing a greater concentration slope over the electrode thickness towards the separator (Fig. S4b). These differences are however less pronounced compared to the KPF<sub>6</sub> experiment due to the electrolyte solutions used. In the KPF<sub>6</sub> experiment, strong diffusive mass transport from the CE to WE results in a steep concentration profile in the NIPS electrode. Conversely, in the experiment containing the

BF<sub>4</sub><sup>-</sup>, migration of the supporting anion through the porous separator is visible because of the high attenuation of this molecule. For the cloth electrode, concentration profiles in the CE and WE do not return to the OCV profiles when the electric field is reversed, due to the capacity not being fully restored. Fixing the potential and time, but not the current, prevents full capacity restoration because of the asymmetry in electrolyte solutions in the tanks. The concentration profiles in the paper (WE) and NIPS electrodes, however, converge towards the OCV profiles as ~4 times fewer active species are converted in these electrodes. Finally, minimal differences in concentration are



Fig. 4 *Operando* neutron imaging of the active species transport with the low attenuating KPF<sub>6</sub> supporting salt for the paper electrode and two flow field designs: parallel and interdigitated, at an inlet flow rate of 5 mL min<sup>-1</sup> and evaluated at OCV, -0.6 V, and +0.6 V. (a) The potential applied and current output of the electrochemical cells. (b) The averaged concentration profiles over time in the counter electrode (CE) and the working electrode (WE). (c) The cumulative active species (TEMPO and TEMPO<sup>+</sup>) concentration profiles over the electrode thickness with the averaged snapshots of the cell after image processing, with on the counter electrode 0.5 M [TEMPO] + [TEMPO<sup>+</sup>PF<sub>6</sub><sup>-</sup>] at 50% state-of-charge in 0.2 M KPF<sub>6</sub> and at the working electrode 0.2 M [TEMPO] + [TEMPO<sup>+</sup>PF<sub>6</sub><sup>-</sup>] at 50% state-of-charge in 0.2 M KPF<sub>6</sub>. Incomplete filling of the flow field channels is highlighted in the snapshots.





correlations with electrochemical performance. Complementary high-resolution techniques such as confocal fluorescence microscopy, electrochemical imaging, or microscale models are therefore essential to resolve local microstructural effects, diffusion boundary layers, local reaction rates, and local electrolyte velocities,<sup>19,24</sup> as well as to validate neutron imaging interpretations.

## Author contributions

M.v.d.H. contributed to the conceptualization, methodology, formal analysis, investigation, data curation, visualization, image processing, writing – original draft, and writing – review and editing. R. R. J. and E. B. B. contributed to the conceptualization, methodology, formal analysis, investigation, data curation, and writing – review and editing. P. B. contributed to the methodology, formal analysis, investigation, data curation, and image processing. Finally, A. F. C. contributed to the conceptualization, methodology, formal analysis, investigation, data curation, funding, resources, writing – original draft, writing – review and editing, project administration, and supervision.

## Conflicts of interest

The authors declare no conflict of interest.

## Data availability

The data presented in this study can be found in the SI or can be provided by the corresponding author upon reasonable request.

The following information can be found in the supplementary information: complete electrochemical and concentration profiles over time for all flow rates and potentials tested for all cell configurations, a statement on the electrode compression, concentration plots to compare the differences between the investigated cell configurations, capacity curves over time, and the main result figure for the supporting ion experiment for the flow field comparison. See DOI: <https://doi.org/10.1039/d5se00844a>.

## Acknowledgements

A. F. C. gratefully acknowledges the Dutch Research Council (NWO) for financial support through the Talent Research Program Veni (17324), the NWO Science XS grant (OCENW.XS4.295), and funding by the European Union (ERC, FAIR-RFB, ERC-2021-STG 101042844). Views and opinions expressed are however those of the author(s) only and do not necessarily reflect those of the European Union or the European Research Council. Neither the European Union nor the granting authority can be held responsible for them. E. B. B. and A. F. C. gratefully acknowledge funding from the Eindhoven Institute of Renewable Energy Systems (EIRES). The results of this project are based on experiments performed at the Swiss Spallation Neutron Source, SINQ, Paul Scherrer Institute (Switzerland), with proposal number 20202189.

## References

- 1 A. Z. Weber, *et al.*, Redox flow batteries: a review, *J. Appl. Electrochem.*, 2011, **41**, 1137–1164.
- 2 P. Leung, *et al.*, Recent developments in organic redox flow batteries: a critical review, *J. Power Sources*, 2017, **360**, 243–283.
- 3 A. Forner-Cuenca, E. E. Penn, A. M. Oliveira and F. R. Brushett, Exploring the role of electrode microstructure on the performance of non-aqueous redox flow batteries, *J. Electrochem. Soc.*, 2019, **166**, A2230–A2241.
- 4 M. Skyllas-Kazacos, M. H. Chakrabarti, S. A. Hajimolana, F. S. Mjalli and M. Saleem, Progress in Flow Battery Research and Development, *J. Electrochem. Soc.*, 2011, **158**, R55.
- 5 E. Sánchez-Díez, *et al.*, Redox flow batteries: Status and perspective towards sustainable stationary energy storage, *J. Power Sources*, 2021, **481**, 228804.
- 6 R. M. Darling, K. G. Gallagher, J. A. Kowalski, S. Ha and F. R. Brushett, Pathways to low-cost electrochemical energy storage: A comparison of aqueous and nonaqueous flow batteries, *Energy Environ. Sci.*, 2014, **7**, 3459–3477.
- 7 M. H. Chakrabarti, *et al.*, Application of carbon materials in redox flow batteries, *J. Power Sources*, 2014, **253**, 150–166.
- 8 M. van der Heijden and A. Forner-cuenca, Transport phenomena and cell overpotentials in redox flow batteries. in *Encyclopedia of Energy Storage*, ed. Cabeza, L. F., Elsevier Inc., Oxford, 2022, pp 480–499 doi:DOI: [10.1016/B978-0-12-819723-3.00132-3](https://doi.org/10.1016/B978-0-12-819723-3.00132-3).
- 9 V. Muñoz-Perales, *et al.*, Investigating the Coupled Influence of Flow Fields and Porous Electrodes on Redox Flow Battery Performance, *J. Power Sources*, 2023, **586**, 233420.
- 10 V. Muñoz-Perales, *et al.*, Understanding the Role of Electrode Thickness on Redox Flow Cell Performance, *ChemElectroChem*, 2024, **11**, e2023003.
- 11 V. Muñoz-Perales, M. van der Heijden, P. Á. García-Salaberri, M. Vera and A. Forner-Cuenca, Engineering Lung-inspired Flow Field Geometries for Electrochemical Flow Cells with Stereolithography 3D Printing, *ACS Sustain. Chem. Eng.*, 2023, **11**, 12243–12255.
- 12 J. D. Milshtein, *et al.*, Quantifying mass transfer rates in redox flow batteries, *J. Electrochem. Soc.*, 2017, **164**, E3265–E3275.
- 13 K. M. Tenny, A. Forner-Cuenca, Y.-M. Chiang and F. R. Brushett, Comparing Physical and Electrochemical Properties of Different Weave Patterns for Carbon Cloth Electrodes in Redox Flow Batteries, *J. Electrochem. Energy Convers. Storage*, 2020, **17**, 041010.
- 14 V. Muñoz-Perales, *et al.*, Investigating the Coupled Influence of Flow Fields and Porous Electrodes on Redox Flow Battery Performance, *J. Power Sources*, 2023, **586**, 233420.
- 15 R. M. Darling and M. L. Perry, The Influence of Electrode and Channel Configurations on Flow Battery Performance, *J. Electrochem. Soc.*, 2014, **161**, A1381–A1387.
- 16 M. Macdonald and R. M. Darling, Comparing velocities and pressures in redox flow batteries with interdigitated and serpentine channels, *AIChE J.*, 2019, **65**, 1–11.



- 17 C. R. Dennison, E. Agar, B. Akuzum and E. C. Kumbur, Enhancing Mass Transport in Redox Flow Batteries by Tailoring Flow Field and Electrode Design, *J. Electrochem. Soc.*, 2016, **163**, A5163–A5169.
- 18 A. A. Wong and M. J. Aziz, Method for Comparing Porous Carbon Electrode Performance in Redox Flow Batteries, *J. Electrochem. Soc.*, 2020, **167**, 110542.
- 19 M. van der Heijden, R. van Gorp, M. A. Sadeghi, J. Gostick and A. Forner-Cuenca, Assessing the versatility and robustness of pore network modelling to simulate redox flow battery electrode performance, *J. Electrochem. Soc.*, 2022, **169**, 040505.
- 20 K. Köble, *et al.*, Synchrotron X-Ray radiography of vanadium redox flow batteries – Time and spatial resolved electrolyte flow in porous carbon electrodes, *J. Power Sources*, 2021, **492**, 229660.
- 21 L. Eifert, *et al.*, Synchrotron X-ray Radiography and Tomography of Vanadium Redox Flow Batteries—Cell Design, Electrolyte Flow Geometry, and Gas Bubble Formation, *ChemSusChem*, 2020, **13**, 3154–3165.
- 22 F. Tariq, *et al.*, Uncovering the mechanisms of electrolyte permeation in porous electrodes for redox flow batteries through real time: *in situ* 3D imaging, *Sustainable Energy Fuels*, 2018, **2**, 2068–2080.
- 23 R. Jarvis, *et al.*, Design of a miniature flow cell for *in situ* x-ray imaging of redox flow batteries, *J. Phys. D Appl. Phys.*, 2016, **49**, 434002.
- 24 A. A. Wong, S. M. Rubinstein and M. J. Aziz, Direct visualization of electrochemical reactions and heterogeneous transport within porous electrodes in *operando* by fluorescence microscopy, *Cell Rep. Phys. Sci.*, 2021, **2**, 100388.
- 25 K. R. Minard, V. V. Viswanathan, P. D. Majors, L. Q. Wang and P. C. Rieke, Magnetic resonance imaging (MRI) of PEM dehydration and gas manifold flooding during continuous fuel cell operation, *J. Power Sources*, 2006, **161**, 856–863.
- 26 Z. Dunbar and R. I. Masel, Quantitative MRI study of water distribution during operation of a PEM fuel cell using Teflon® flow fields, *J. Power Sources*, 2007, **171**, 678–687.
- 27 E. W. Zhao, *et al.*, Coupled *in Situ* NMR and EPR Studies Reveal the Electron Transfer Rate and Electrolyte Decomposition in Redox Flow Batteries, *J. Am. Chem. Soc.*, 2021, **143**, 1885–1895.
- 28 E. W. Zhao, *et al.*, In situ NMR metrology reveals reaction mechanisms in redox flow batteries, *Nature*, 2020, **579**, 224–228.
- 29 J. T. Clement *Investigation of Localized Performance and Gas Evolution in All-Vanadium Redox Flow Batteries via In Situ Distributed Diagnostic Techniques*, University of Tennessee, 2016. doi:[https://trace.tennessee.edu/utk\\_graddiss/4089](https://trace.tennessee.edu/utk_graddiss/4089).
- 30 R. R. Jacquemond, *et al.*, Quantifying concentration distributions in redox flow batteries with neutron radiography, *Nat. Commun.*, 2024, **15**, 7434.
- 31 L. Bohn, *et al.*, High-Resolution Neutron Imaging of Water Transport in CO<sub>2</sub> Electrolysis during Pulsed Operation, *ACS Energy Lett.*, 2025, **10**, 975–981.
- 32 J. Disch, *et al.*, High-resolution neutron imaging of salt precipitation and water transport in zero-gap CO<sub>2</sub> electrolysis, *Nat. Commun.*, 2022, **13**, 6099.
- 33 S. J. Altus, B. J. Inkson and J. Hack, Complementary X-ray and neutron imaging of water electrolysers for green hydrogen production, *J. Mater. Chem. A*, 2024, **12**, 23364–23391.
- 34 J. Wood, in *Computational Methods in Reactor Shielding*, Elsevier Ltd, United Kingdom, 1982. doi:DOI: [10.1016/b978-0-08-028685-3](https://doi.org/10.1016/b978-0-08-028685-3).
- 35 P. Rinard, in *Neutron Interactions with Matter*, 1997, pp 357–377.
- 36 C. T. C. Wan, R. R. Jacquemond, Y. M. Chiang, A. Forner-Cuenca and F. R. Brushett, Engineering Redox Flow Battery Electrodes with Spatially Varying Porosity Using Non-Solvent-Induced Phase Separation, *Energy Technol.*, 2023, **11**, 2300137.
- 37 C. T. Wan, *et al.*, Non-Solvent Induced Phase Separation Enables Designer Redox Flow Battery Electrodes, *Adv. Mater.*, 2021, **33**, 2006716.
- 38 V. F. Sears, Neutron scattering lengths and cross sections, *Neutron News*, 1992, **3**, 26–37.
- 39 E. H. Lehmann, P. Vontobel and L. Wiesel, Properties of the radiography facility NEUTRA at SINQ and its potential for use as European reference facility, *Nondestr. Test. Eval.*, 2001, **16**, 191–202.
- 40 P. Boillat, G. Frei, E. H. Lehmann, G. G. Scherer and A. Wokaun, Neutron imaging resolution improvements optimized for fuel cell applications, *Electrochem. Solid-State Lett.*, 2010, **13**, 68–71.
- 41 E. R. C. Ruiz, *et al.*, Spectroscopic Neutron Imaging for Resolving Hydrogen Dynamics Changes in Battery Electrolytes, *Mater. Today Adv.*, 2023, **19**, 100405.
- 42 J. D. Milshtein, J. L. Barton, R. M. Darling and F. R. Brushett, 4-Acetamido-2,2,6,6-Tetramethylpiperidine-1-Oxyl As a Model Organic Redox Active Compound for Nonaqueous Flow Batteries, *J. Power Sources*, 2016, **327**, 151–159.
- 43 J. L. Barton, J. D. Milshtein, J. J. Hinricher and F. R. Brushett, Quantifying the impact of viscosity on mass-transfer coefficients in redox flow batteries, *J. Power Sources*, 2018, **399**, 133–143.
- 44 M. van der Heijden, G. Szendrei, V. de Haas and A. Forner-Cuenca, A versatile optimization framework for porous electrode design, *Digital Discovery*, 2024, **3**, 1292–1307.
- 45 R. R. Jacquemond, R. Geveling, A. Forner-Cuenca and K. Nijmeijer, On the Characterization of Membrane Transport Phenomena and Ion Exchange Capacity for Non-Aqueous Redox Flow Batteries, *J. Electrochem. Soc.*, 2022, **169**, 080528.
- 46 X. G. Yang, Q. Ye, P. Cheng and T. S. Zhao, Effects of the electric field on ion crossover in vanadium redox flow batteries, *Appl. Energy*, 2015, **145**, 306–319.
- 47 P. Kurzweil and M. Chwistek, Electrochemical stability of organic electrolytes in supercapacitors: Spectroscopy and gas analysis of decomposition products, *J. Power Sources*, 2008, **176**, 555–567.
- 48 X. Ke, *et al.*, Rechargeable redox flow batteries: Flow fields, stacks and design considerations, *Chem. Soc. Rev.*, 2018, **47**, 8721–8743.

