


 Cite this: *Nanoscale*, 2024, **16**, 16048

Ditopic ligand effects on solution structure and redox chemistry in discrete $[\text{Cu}_{12}\text{S}_6]$ clusters with labile Cu–S bonds†

 Michael J. Trenerry  and Gwendolyn A. Bailey *

Copper chalcogenide nanoclusters (Cu–S/Se/Te NCs) are a broad and diverse class of atomically precise nanomaterials that have historically been studied for potential applications in luminescent devices and sensors, and for their beautiful, mineral-like crystal structures. By the “cluster-surface” analogy, Cu–S/Se NCs are prime candidates for the development of nanoscale multimetallic catalysts with atomic precision. However, the majority of studies conducted to date have focused exclusively on their solid-state structures and physical properties, leaving open questions as to their solution stability, dynamics, and reactivity. Herein, we report the first detailed interrogation of solution structure, dynamics, electrochemistry, and decomposition of Cu–S NCs. Specifically, we report the detailed NMR spectroscopy, diffusion-ordered spectroscopy, MALDI mass spectrometry, electrochemical and stoichiometric redox reactivity studies, and DFT studies of a series of $[\text{Cu}_{12}\text{S}_6]$ clusters with labile Cu–S bonds supported by monodentate phosphines and ditopic bis(diphenylphosphino)alkane ligands PPh_2R (R = Et, $-(\text{CH}_2)_5-$, $-(\text{CH}_2)_8-$). We find that the ligand binding topology dictates the extent of speciation in solution, with complete stability being afforded by the longer octane chelate in *dppo* (1,8-bis(diphenylphosphino)octane) according to ^1H and DOSY NMR and MALDI-MS studies. Furthermore, a combined electrochemical and computational investigation of $[\text{Cu}_{12}\text{S}_6(\text{dppo})_4]$ reveals that the intact $[\text{Cu}_{12}\text{S}_6]$ core undergoes a quasireversible one-electron oxidation at mild applied potentials ($[\text{Cu}_{12}\text{S}_6]^{0/+}$: -0.50 V vs. $\text{Fc}^{0/+}$). In contrast, prolonged air exposure or treatment with chemical oxidants results in cluster degradation with S atom extrusion as phosphine sulfide byproducts. This work adds critical new dimensions to the stabilization and study of atomically precise metal chalcogenide NCs with labile M–S/Se bonds, and demonstrates both progress and challenges in controlling the solution behaviour and redox chemistry of phosphine-supported copper chalcogenide nanoclusters.

 Received 25th June 2024,
Accepted 22nd July 2024

DOI: 10.1039/d4nr02615b

rsc.li/nanoscale

Introduction

Base metal sulfides are some of Nature’s most ancient and ubiquitous catalysts capable of cooperatively activating and converting small, traditionally inert molecules into valuable products.^{1–5} Understanding and controlling the interaction of small molecules at the surface is important for tailoring the reactivity of a system, *e.g.* towards improved selectivity, turnover, and robustness.^{6,7} Unfortunately, the factors governing activity and selectivity are often elusive and complex, sometimes varying according to subtle differences in material preparation, crystallinity, or composition.^{8,9}

In this context, metal chalcogenide nanoclusters (NCs) have shown significant promise for development of earth-abundant, multimetallic catalyst systems with atomistic control.^{10–12} These NCs capture the essential features of bulk metal chalcogenides, including their highly delocalized electronic structures and flexible configuration of multimetallic active sites.^{13–25} Additionally, their discrete, atomically precise structures confer some distinct advantages. First, NCs feature well-defined arrangements of surface ligands that can be tuned to manipulate active site steric environments, secondary coordination sphere interactions, and NC electronic character. Additionally, the configuration and number of core atoms can be known precisely and varied systematically to improve catalyst performance.^{9,26–29} Finally, NCs incorporate a higher density of active surface sites, leading to higher turnover frequencies relative to analogous surfaces. For example, Besenbacher and coworkers showed that $[\text{Mo}_3\text{S}_{13}]^{2-}$ NCs supported on highly ordered pyrolytic graphite catalyzed the

University of Minnesota – Twin Cities, Minneapolis, MN 55455, USA.

 E-mail: gbailey@umn.edu

 †Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4nr02615b>

hydrogen evolution reaction with roughly an order of magnitude greater turnover frequency than either amorphous or nanocrystalline MoS₂.⁹ Similarly, Zang and coworkers evaluated the electrocatalytic CO₂ reduction activity of a thiolate-supported ditetrahedron-shaped Cu₈ cluster, finding that the Faradaic efficiencies for generation of formate exceeded that of an isomeric cube-shaped cluster by up to 1.5-fold.²⁸ In related studies, the photocatalytic activity of thiopyrimidine-supported Cu₆ clusters for CO₂ reduction to CO was enhanced by the presence of the thiopyrimidine group, which acted as a proton relay.³⁰ Clearly, there is enormous potential to develop multimetallic catalysts with unprecedented control *via* changes to the NC core composition, size, morphology, active site structure, ligand configuration, and ligand structure.

While extensive research has focused on understanding and developing catalytically active NCs of M–S/Se where M = Fe, Mo, W, and others,^{3,9,31–38} examples of Cu–S/Se NCs remain rare.^{39–42} This is despite recent compelling evidence that S/Se-modified Cu phases are highly active for electrocatalytic CO₂ reduction (eCO₂R) to high-value liquid products.^{43–51} According to these reports, the incorporation of chalcogenide improves product selectivity by shutting down the formation of H₂ and boosting the production of formate, methane, acetic acid, and C₂–C₃ alcohols. Still, the origins of product selectivity, including the mechanistic details of catalyst turnover and structural requirements for selective turnover, are under debate.^{44–46,49–53} Moreover, facile and dynamic changes to the surface structure under catalytic conditions further complicate tuning by modification of catalyst structure.^{46,49,50,53} Discrete NCs of Cu–S/Se have the potential to offer improved understanding and rational control over multimetallic architectures, and they are accessible in a wide range of core configurations and sizes that rival the structural complexity of the bulk solids.^{54–56} While such flexibility facilitates the identification of specific, discrete active sites, it also presents a challenge due to the inherent Cu–S/Se bond lability and hence cluster instability.^{57–60} Indeed, most studies of Cu–S/Se NCs have focused exclusively on their synthesis and solid-state properties, including their crystallographic structures and photoluminescence.^{54–56,61,62} Better understanding of the solution behavior and redox properties of discrete Cu–S/Se NCs is needed to inform the development of robust molecular congeners of catalytically active bulk surfaces.

To this end, the [Cu₁₂S₆] core configuration presents an interesting test case. One of the earliest derivatives, [Cu₁₂S₆(PET₃)₈] (**1**·PET₃), was reported to decompose in solution at –20 °C as evidenced by the brown colour of diethyl ether solutions from which violet crystals of **1**·PET₃ were isolated.⁵⁷ In contrast, ditopic bis(diphenylphosphino)alkane ligands such as **dp**po and **dp**pt (1,8-bis(diphenylphosphino)octane) and 1,5-bis(diphenylphosphino)pentane, respectively) appear to impart some stability, according to rare electronic absorption and emission studies in THF.^{58,59} For [Cu₁₂S₆(dppo)₄] (**1**·dppo, Fig. 1), bright red phosphorescence was observed with emission maxima centered at 640 and 655 nm (λ_{ex} = 350 and 455 nm, respectively), consistent with an intact [Cu₁₂S₆]

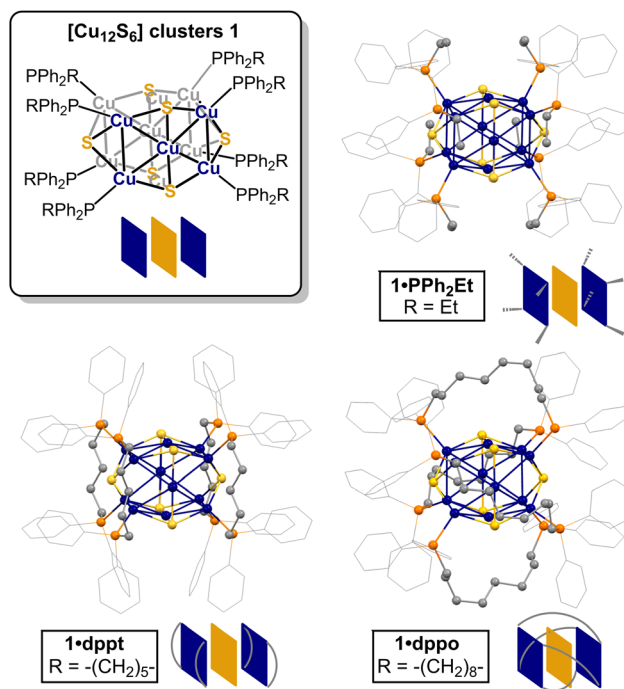


Fig. 1 Structures of [Cu₁₂S₆] clusters **1** supported by alkyl diphenylphosphine ligands: ball and stick diagrams and cartoon representations of **1**·PPH₂Et (top right), **1**·dppt (bottom left), and **1**·dppo (bottom right) showing ditopic ligand binding mode (adapted from reported crystallographic data^{59,61}). Colour scheme: grey (C); orange (P); blue (Cu); yellow (S). H atoms omitted for clarity. PPh₂Et: diphenylethylphosphine; dppt: 1,5-bis(diphenylphosphino)pentane; dppo: 1,8-bis(diphenylphosphino)octane.

core.⁵⁹ For [Cu₁₂S₆(dppt)₄] (**1**·dppt), however, the solution spectrum exhibited an additional emission maximum centered at 750 nm (λ_{ex} = 425 nm) not present in solid-state spectra, consistent with at least partial speciation. While suggestive, these studies can only confirm the presence of intact clusters and cannot necessarily detect other species that may have formed in solution. Moreover, the details of the solution structure, dynamics, and origin of improved stability for **1**·dppo remain unclear.

Herein, we present a systematic study of solution structure, dynamics, and redox properties of [Cu₁₂S₆] clusters **1** *via* ¹H/³¹P{¹H} NMR and diffusion-ordered spectroscopy, MALDI-MS, and electrochemistry. These studies unequivocally confirm that **1**·dppo remains fully intact in THF-d₈ solutions and reveal previously unrecognized subtleties in the stabilization of [Cu₁₂S₆] by dppo, including the retention of a rigid, conformationally locked ligand configuration in solution and the potential role of bridging CH...S interactions in stabilizing the ligands in place. In addition, combined electrochemical, computational (DFT), and stoichiometric oxidation studies reveal that **1**·dppo can support a chemically reversible [Cu₁₂S₆]^{0/+} redox couple—an important prerequisite for electrocatalytic studies. However, chemical oxidation rapidly triggers intramolecular S atom transfer and elimination of the support-

ing **dppo** ligands as phosphine sulfide products (**dppoS** and/or **dppoS₂**) alongside cluster decomposition. Combined, these studies shed light on the structural vulnerabilities of the [Cu₁₂S₆] core and emergent design principles of Cu-S/Se NCs as discrete molecular analogues of some of the leading multi-metallic catalysts for eCO₂R to valuable products.

Results and discussion

Solution structure of [Cu₁₂S₆] clusters **1**

According to the crystallographic metrics, the [Cu₁₂S₆] core of clusters **1** consists of a stretched S₆ octahedron interpenetrated within a Cu₁₂ cuboctahedron, where the cuboctahedron is axially elongated due to phosphine coordination at the eight Cu edge sites.⁶¹ The result is an overall prolate core configuration with two axial Cu₄S pyramids (blue squares, Fig. 1) separated by a central Cu₄S₄ equator (yellow squares). In the solid state, **dppo** and **dppt** bind to the [Cu₁₂S₆] core in one of two preferential coordination modes: in **1-dppo**, the longer octane linker bridges diagonally across each Cu₅S₂ face (avg. $d_{\text{Cu-Cu}} = 5.06 \text{ \AA}$), while in **1-dppt**, the pentane linker is too short to bridge in this coordination mode and is thus confined to binding adjacent Cu sites within the axial Cu₄S pyramid substructures (avg. $d_{\text{Cu-Cu}} = 2.86 \text{ \AA}$).⁵⁹

Prior solution characterization of clusters **1** is confined to the room-temperature electronic absorption and photoluminescence excitation/emission spectra for **1-dppt** and **1-dppo** in THF, as noted above.⁵⁹ To better understand the unusual stability of **1-dppo**, we performed detailed ¹H, ³¹P{¹H}, and diffusion-ordered spectroscopy (DOSY) NMR studies in THF-d₈. Remarkably, the NMR data for **1-dppo** not only confirms that the [Cu₁₂S₆] core is conserved in solution but indicates a highly symmetrical, locked ligand configuration. Thus, the ³¹P{¹H} and ¹H NMR spectra of **1-dppo** reveal a single set of **dppo** resonances distinct from those of the free ligand, consistent with ligand binding in a C₄ symmetry about the cluster core. Notably, each pair of geminal protons within the octyl chain of **dppo** is split into distinct diastereotopic signals CH_aH_b (Fig. 2a; bottom), suggesting constrained ligand rotation upon binding. This effect is most pronounced for the α and β methylene protons, which are more rigorously locked into different chemical environments facing towards or away from the [Cu₁₂S₆] core.

Likewise, the two Ph rings in each PPh₂R group are rendered chemically inequivalent, resulting in two distinct sets of *o*, *m*, and *p*-CH signals (Fig. 2a; top). Of note, one set of *o*-CH signals is shifted significantly downfield at 8.45 ppm (vs. 7.45 ppm in the free ligand), suggesting that these protons may be directly interacting with the core. However, we see no evidence of close CH...Cu interactions in the crystallographic metrics, suggesting that the Cu is too far to participate in an anagostic interaction⁶³ (CH...Cu: 3.10–3.27 Å for one set of *o*-CH). In contrast, the *o*-CH...S contacts between the cisoid Ph pointed towards the cluster and apical Cu₄S are short (CH...S: 2.78 ± 0.20 Å; ∠142–164°;⁵⁹ Fig. 2b). These distances fall in the



Fig. 2 Top: (a) ¹H NMR spectrum (THF-d₈, 400 MHz) of **1-dppo** showing a conformationally locked ligand configuration about [Cu₁₂S₆] (³THF solvent, *residual pentane). Ph *o*/*m*/*p*-CH signals belonging to cisoid versus transoid Ph rings are denoted with *c* and *t* subscripts, respectively. Bottom: truncated crystallographic structures of **1-dppo** showing CH...S interactions and representative distances with (b) Ph *o*-CH; (c) α-CH_a. Colour scheme: dark grey (cisoid Ph-C); light grey (transoid Ph-C); orange (P); blue (Cu); yellow (S); white (H). H atoms are omitted except cisoid Ph *o*-CH and octane α-CH_a, which are shown interacting with S.

lower range of CH...S contacts found in the crystal structure database for metal complexes of group 11 and may reflect an attractive CH...S interaction (typical CH...S: 2.84–3.40 Å; ∠144–180° & 117–135°).⁶⁴ Short CH...S contacts are also observed in the crystal structures of **1-dppt** and **1-PPh₂Et** (**1-dppt**: 2.92 ± 0.21 Å; **1-PPh₂Et**: 2.87 ± 0.12 Å), although these clusters do not remain intact in solution (*vide infra*).

Similarly, one diastereotopic α-CH_aH_b signal is shifted downfield at 2.71 ppm (vs. 2.02 ppm in free **dppo**), consistent with weaker but still appreciable CH...S interactions with the central sulfides, as reflected in the crystallographic metrics (CH...S: 3.18 ± 0.23 Å, ∠117 ± 4°; Fig. 2c). By contrast, the β-CH_b signal is shifted substantially upfield at 0.15 ppm (*versus* 2.02 ppm in the free ligand), suggesting a possible CH...Cu agostic interaction. However, close CH...Cu contacts were not observed with any of the neighbouring Cu in the crystallographic coordinates (average CH...Cu: 3.12 ± 0.18 Å; range 2.77–3.84 Å), perhaps reflecting the impact of crystal packing and/or solvent effects on the interaction of β-CH_b with the cluster core.

In comparison, the solution ¹H NMR signals for samples of **1-dppt** and **1-PPh₂Et** are broadened and shifted slightly upfield, but otherwise show little change relative to the respective free ligands, consistent with fluxional coordination to electron-rich Cu(I) centers ($\omega_{1/2}$ 21.3 Hz and 17.3 Hz,

respectively, for the most downfield signal; Fig. 3b). Solution-phase equilibria with smaller clusters and/or monometallic species is confirmed by the ^1H DOSY NMR spectra, which reveal significantly larger diffusion coefficients than expected for the intact clusters, indicating a smaller radius on average for these fluxional species (e.g. **1-PPh₂Et**, Fig. 3b: $D = 11.0 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$; $r_{\text{DOSY}} = 4.3 \text{ \AA}$; cf. $r_{\text{XRD}} = 8.8 \text{ \AA}$ estimated from the XRD structure; see the ESI† for details). These results contrast the ^1H DOSY NMR spectrum of **1-dppo**, which exhibits a single uniform and exceptionally small diffusion coefficient for all non-solvent ^1H NMR signals in close agreement with the expected value for an intact cluster (Fig. 3a: $D = 5.1 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$; $r_{\text{DOSY}} = 9.4 \text{ \AA}$; cf. $r_{\text{XRD}} \approx 9.4 \text{ \AA}$).⁵⁹ Further evidence for the intact $[\text{Cu}_{12}\text{S}_6]$ core was obtained by MALDI-MS analysis, in which samples were dropcast from THF solutions and cocrystallized with the charge-transfer matrix anthracene (base peak: $[\text{Cu}_{12}\text{S}_6(\text{dppo})_2]^+$ m/z 1919.5 Da, expected 1919.4 Da; see Fig. S1 and S2† for details).

Combined, these studies shed light on the unique ability of the **dppo** ligand to stabilize and enforce rigidity of the $[\text{Cu}_{12}\text{S}_6]$ core. Clusters **1** are inherently unstable structures that speciate spontaneously in solution due to the lability of core Cu–S bonds. By contrast, the rigid, conformationally locked ligand configuration in **1-dppo** is likely responsible for its improved core stability. The **dppo** ligand spans diagonally across each $[\text{Cu}_5\text{S}_2]$ cluster face of **1-dppo** and in doing so, supports the cluster along all 3 axes (Fig. 1 above). This includes stabilizing the weaker Cu–S linkages that extend between the axial Cu and equatorial S, which are notably elongated in the crystallographic coordinates (Cu–S: 2.36–2.40 Å, vs. 2.14–2.27 Å in the apical and equatorial linkages, see ESI† for details).^{59,61} In

contrast, the shorter pentyl linker of **dppt** permits binding at only adjacent apical Cu sites, leaving the vulnerable Cu–S bonds liable for breakage. These studies emphasize the importance of long, ditopic linkers in buttressing the vulnerable axes of labile Cu–S/Se NCs and ultimately ensuring solution stability. Moreover, they demonstrate that while $\text{CH}\cdots\text{S}$ interactions may play a stabilizing role in locking the **dppo** ligand in place, they are likely not the primary cause of the stability of **1-dppo**.

Solution electrochemistry studies

The distinct stability of **1-dppo** presents an opportunity to study the solution-phase electrochemistry of the $[\text{Cu}_{12}\text{S}_6]$ core. Thus, **1-dppo** exhibits an irreversible reduction with cathodic peak potential at $-3.2 \text{ V vs. Fe}^{0/+}$, suggesting that partial Cu(0) character may be electrochemically accessible though transient in the $[\text{Cu}_{12}\text{S}_6]$ core (red trace, Fig. 4). We also observe a quasireversible redox couple at $-0.50 \text{ V vs. Fe}^{0/+}$, which we assign to the one-electron oxidation of the $[\text{Cu}_{12}\text{S}_6]$ core ($[\text{1-dppo}]^{0/+}$; red trace, Fig. 4). Further, irreversible oxidation events occur at potentials more positive than $-0.25 \text{ V vs. Fe}^{0/+}$ (dotted pink trace). Scanning beyond -0.25 V also causes the cathodic return wave of the $[\text{1-dppo}]^{0/+}$ redox couple to become diminished, indicating that **1-dppo** is highly sensitive to oxidizing conditions and likely degrades following loss of more than one electron. A similar phenomenon was recently reported for the carbene-stabilized Cu_4S cluster, $[\text{Cu}_4\text{S}(\text{L})_2]^{2+}$, which is structurally analogous to the apical Cu_4S pyramids in **1-dppo** ($E_{1/2}[\text{Cu}_4\text{S}(\text{L})_2]^{2+/3+}$: $-0.65 \text{ V vs. Fe}^{0/+}$; L = a tetracarbene ligand).⁶⁵ The free **dppo** ligand similarly undergoes irreversible oxidation



Fig. 3 ^1H DOSY NMR spectra (THF- d_8 , 400 MHz) of (a) **1-dppo** and (b) **1-PPh₂Et** showing the unique ability of the **dppo** ligand to arrest speciation of the $[\text{Cu}_{12}\text{S}_6]$ cluster core. Dashed line in (b) indicates the calculated diffusion coefficient for intact **1-PPh₂Et** based on the crystallographic structure.⁶¹



Fig. 4 Cyclic voltammograms (top) and differential pulse voltammograms (bottom) of **1-dppo** (1 mM concentration, red and dotted pink traces) and free **dppo** ligand (5 mM concentration, blue trace). Collected at 20 mV s^{-1} in THF with 100 mM tetrabutylammonium hexafluorophosphate ($[\text{Bu}_4\text{N}][\text{PF}_6]$) electrolyte.

at mildly anodic potentials (blue trace), with a smaller pre-wave feature beginning at -0.2 V vs. $\text{Fc}^{0/+}$ that aligns with the onset of irreversible oxidations in **1-dppo**. However, a sharp increase in current is only observed at potentials of 0.5 V and higher, whereas in **1-dppo** the irreversible features are cathodically shifted by *ca.* 250 mV. We thus conclude that the degradation of **1-dppo** ultimately stems from oxidation of the composite cluster, rather than its supporting ligands exclusively, at distinctly milder conditions.

We next targeted the putative oxidized cluster $[\mathbf{1-dppo}]^+$ via chemical oxidation using $[\text{Cp}^*_2\text{Fe}][\text{PF}_6]$ (Cp^* = pentamethylcyclopentadienyl; $E_{1/2}$: -0.44 V in THF). $[\text{Cp}^*_2\text{Fe}]^+$ was chosen as a mild oxidant to avoid over-oxidation of the $[\text{Cu}_{12}\text{S}_6]$ core and ensuing decomposition. Nevertheless, by ^1H and $^{31}\text{P}\{^1\text{H}\}$ NMR we observe the complete disappearance of **1-dppo** only upon the addition of two equivalents of oxidant (Fig. 5a). This change is accompanied by the growth of new, diagnostic ^{31}P NMR signals at *ca.* 41.8 and 42.0 ppm and a downfield ^1H NMR signal at 7.95 ppm. Assignment of these spectral features as 1,8-bis(diphenylphosphino)octane sulfides ($\text{Ph}_2\text{RP}=\text{S}$: dppoS and/or dppoS₂), presumably originating from oxidation of the parent dppo ligand, is confirmed by independent synthesis (see the ESI† for details). A broad ^{31}P NMR signal ranging from -7 to -9 ppm and a ^1H NMR multiplet at ~ 7.4 ppm also grow in with additional equivalents of oxidant. We assign these signals to remaining dppo ligands bound to the Cu sites of cluster degradation products.

By quantitative ^1H NMR measurements (Fig. 5b), we find that the oxidation of **1-dppo** with two equiv. $[\text{Cp}^*_2\text{Fe}]^+$ yields

ca. 1 phosphine sulfide group per starting cluster. Importantly, the conversion of phosphine to phosphine sulfide is a two-electron oxidation and is thus consistent with the complete disappearance of **1-dppo** after the addition of two equivalents of oxidant, as well as the electrochemical measurements above indicating loss of reversibility following oxidation by more than one electron. Overoxidation in the presence of the comparatively mild oxidant $[\text{Cp}^*_2\text{Fe}]^+$ likely reflects spontaneous disproportionation of the putative one-electron oxidized species $[\mathbf{1-dppo}]^+$. Minor growth of phosphine sulfide continues following the addition of >2 equivalents of $[\text{Cp}^*_2\text{Fe}][\text{PF}_6]$, suggesting a reaction between the remaining sulfides of cluster decomposition products and residual dppo and/or dppoS. Interestingly, phosphine sulfide is also observed as a byproduct following air oxidation of solution samples of **1-dppo**, indicating that this decomposition pathway is also active under aerobic conditions. ^1H DOSY analysis of the air-oxidized species reveals that the products formed on air oxidation correspond to species that are smaller than **1-dppo** itself (Fig. S21 and S22†).

Electronic structure calculations

Geometry optimization and electronic structure calculations were carried out using density functional theory (DFT) to probe the nature of redox events and degradation under oxidizing conditions. We performed these calculations on the model species $[\mathbf{1'-PPh}_2\text{Et}]^{0/+2+}$ in which the dppo ligands are truncated as separate PPh_2Et ligands for the sake of computational cost. Importantly, the relative orientations of phosphines are preserved from **1-dppo**, making the structure of $\mathbf{1'-PPh}_2\text{Et}$ distinct from **1-PPh₂Et**. The highest occupied molecular orbitals of $\mathbf{1'-PPh}_2\text{Et}$ span a narrow energetic window and primarily depict antibonding interactions between Cu sites and neighboring atoms (Fig. 6). These orbitals are relatively delocalized across the $[\text{Cu}_{12}\text{S}_6]$ core but are best categorized as having predominantly Cu-P σ^* , equatorial S_{3p} , and apical S_{3p} character. Importantly, the HOMO and HOMO-1 of $\mathbf{1'-PPh}_2\text{Et}$ comprise a pseudo-degenerate pair featuring prominent Cu-P σ^* interactions between apical Cu sites and binding phosphines, as well as minor Cu-Cu σ^* interactions between apical and equatorial Cu sites. Minor electron density is also placed on apical sulfides, which are out of phase with neighboring Cu and P sites.

Electronic structure calculations of the oxidized clusters $[\mathbf{1'-PPh}_2\text{Et}]^+$ and $[\mathbf{1'-PPh}_2\text{Et}]^{2+}$ reveal broadly similar trends, with predominantly Cu-P and Cu-Cu σ^* character in the frontier orbitals. Accordingly, oxidation constricts the $[\text{Cu}_{12}\text{S}_6]$ core in $[\mathbf{1'-PPh}_2\text{Et}]^+$ and $[\mathbf{1'-PPh}_2\text{Et}]^{2+}$, giving overall shorter Cu-Cu and Cu-S bond lengths and conferring substantial partial positive charge to the P atoms (Table S6†). Collectively, these effects prime the phosphines for interaction with nearby bridging sulfides, which we infer to be strongly nucleophilic based on the prominent S_{3p} character of the next highest energy-occupied molecular orbitals (*e.g.*, HOMO-1 and HOMO-2 of $[\mathbf{1'-PPh}_2\text{Et}]^{2+}$; Fig. 7). This results in facile nucleophilic attack of a nearby sulfide, culminating in net loss of sulfur and phos-



Fig. 5 (a) Reaction of **1-dppo** with $[\text{Cp}^*_2\text{Fe}][\text{PF}_6]$ (b) concentrations of **1-dppo** (red trace) and phosphine sulfide products dppoS₁₋₂ (black trace), expressed in terms of phosphorus atom equivalents, are plotted versus equivalents of $[\text{Cp}^*_2\text{Fe}][\text{PF}_6]$ added. (c) ^1H NMR spectra (THF-*d*₈, 400 MHz) collected for **1-dppo** with *n* equivalents of $[\text{Cp}^*_2\text{Fe}][\text{PF}_6]$ added. Diagnostic *o*-CH proton signals used to construct the plot in part (b) are highlighted for both **1-dppo** (red) and phosphine sulfides dppoS₁₋₂ (grey).



Fig. 6 Calculated molecular orbital diagram (DFT: BP86/def2-SVP) for the truncated model complex [1'-PPh₂Et] showing the highest occupied molecular orbitals.



Fig. 7 (a) Proposed pathway for decomposition of [Cu₁₂S₆] via oxidative P=S bond formation. (b) Calculated HOMO-1 and HOMO-2 (DFT: BP86/def2-SVP) of [1'-PPh₂Et]²⁺ showing significant S_{3p} orbital character on nearby bridging sulfides.

phine as a phosphine sulfide and decomposition of the sulfur-deficient [Cu₁₂S₅]²⁺ core.

The oxidative decomposition behavior of **1-dppo** is reminiscent of a similar pathway observed for the phosphine-supported copper hydride cluster [(PPh₃)₆Cu₆H₆], which also exhibits a reversible one-electron oxidation ($E_{1/2} = 1.01$ V vs. Fc^{0/+}) and an irreversible second oxidation event ($E_{pa} = -0.57$ V vs. Fc^{0/+}).⁶⁶ Treatment of [(PPh₃)₆Cu₆H₆] with two equivalents of [Cp₂*Fe]⁺ results in net hydride loss to yield [(PPh₃)₆Cu₆H₅]⁺, presumably *via* deprotonation of the putative dicationic intermediate [(PPh₃)₆Cu₆H₆]²⁺.⁶⁷ In both [(PPh₃)₆Cu₆H₆] and **1-dppo**, structural changes to the cluster core occur only following two-electron oxidation and ensuing group transfer, either of a sulfur atom or a proton. These results are also in line with recent studies of the highly oxidized, all-ferric iron-sulfur clusters [Fe₄S₄(SAR)₄]⁰, which to date have been only isolated in the presence of bulky thiolate ligands that presumably protect the core from decomposition *via* bimolecular pathways (e.g., Ar = 2,6-bis(mesityl)phenyl; $E_{1/2}$ [Fe₄S₄(SAR)₄]^{1-/0}: -0.19 V vs. Fc^{0/+}).^{68,69} Thus, the oxidative sensitivity of metal-sulfur clusters is likely a more general phenomenon that necessitates judicious application of ligands that modulate the electronic structure towards greater inherent robustness of oxidized states. For example, Mankad and coworkers have employed electron-rich, ditopic formamidinate and triazenide ligands to support reduction and disproportionation of N₂O by [Cu₄S] clusters *via* a [Cu₄S]^{3+/4+} redox couple ($E_{1/2} = -1.28$ V vs. Fc^{0/+}).^{23,40,42} [Cu₄S]²⁺ clusters supported by ditopic bis(diphenylphosphino)amine ligands also promote reduction of N₂O to N₂, but require a protic methanol solvent for activation.⁴¹ Similar strategies are likely to be effective for higher nuclearity copper-sulfur clusters such as [Cu₁₂S₆] and are currently being explored in our laboratories.

Conclusions

We report herein the first detailed study of solution structure, dynamics, and electrochemistry of [Cu₁₂S₆] NCs with varied monotopic and ditopic supporting phosphine (PPh₂R) ligands. Importantly, these clusters bear labile Cu-S bonds and thus present a stringent test case for the ability of ditopic ligands to stabilize vulnerable cluster configurations. Our studies rigorously demonstrate that the longer octyl linker in [Cu₁₂S₆(dppo)₄] **1-dppo** results in striking robustness as demonstrated by solution ¹H, ³¹P{¹H}, and DOSY NMR studies in THF-d₈, in contrast to shorter linkers or monotopic phosphines in other structurally related clusters. In addition, while the ¹H NMR and crystallographic data indicate the presence of relatively strong CH...S interactions in **1-dppo**, these interactions do not appear to be solely responsible for the unique stability of **1-dppo** and instead may assist by enforcing a rigid ligand conformation about [Cu₁₂S₆]. These results are important considering recent evidence supporting the significance of CH...SR interactions (R = alkyl, aryl; S = monovalent or divalent sulfur) in controlling the behaviour of enzymes, metal

complexes, and supramolecular assemblies.⁶⁴ In contrast, the role of CH...S interactions in stabilizing cluster assemblies bearing bridging S²⁻ ligands has been studied in far less detail.⁶⁴

Moreover, our in-depth electrochemical investigations have demonstrated the [Cu₁₂S₆] core of **1-dppo** to be redox-active, exhibiting a quasireversible [Cu₁₂S₆]^{0/+} redox couple at mildly oxidizing potentials (−0.50 V vs. Fe^{0/+}). Unfortunately, attempts at isolating this putative oxidized species resulted in facile S atom transfer and elimination of **dppo** supporting ligands as phosphine sulfides (Ph₂RP=S) with ultimate decomposition of the cluster. Collectively, these results underscore both challenges and opportunities in leveraging Cu–S/Se NCs for electrocatalytic studies. First, labile ligands such as phosphines must be reinforced by multitopic binding, ideally across multiple axes of the core. Second, while one- and two-electron oxidations are electrochemically accessible at mild potentials, the oxidized clusters are unstable entities that decompose *via* extrusion of Ph₂RP=S. This inherent limitation of phosphine-supported Cu–S/Se NCs highlights the importance of new cluster discovery towards extending truly functional, *catalytic* behavior to the atomically precise nanoscale. Specifically, there is a need to explore alternative, tailor-designed ligand sets that resist both speciation and decomposition *via* S-atom extrusion by leveraging the effects of specific ditopic ligand coordination modes explored in this work in combination with other features, such as stronger ligand binding to Cu sites and local steric environments that favor cluster core morphologies with different arrangements of bridging sulfides.

Author contributions

M. J. T. and G. A. B. conceived and planned the experiments. M. J. T. performed the synthesis of all compounds, collected experimental data, and performed DFT calculations. M. J. T. and G. A. B. jointly wrote the manuscript.

Data availability

Data for this article, including ¹H, ³¹P{¹H}, and DOSY NMR spectra, MALDI mass spectra, electrochemical data, powder X-ray diffraction data, computational details, and Cartesian coordinates of DFT-optimized structures, have been included as part of the ESI.†

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research was supported by startup funds through the University of Minnesota – Twin Cities. Powder X-ray diffraction

experiments were carried out in the Characterization Facility at the University of Minnesota, which receives partial support from the NSF through the MRSEC (#DMR-2011401) and the NNCI (#ECCS-2025124) programs. NMR and MS experiments were carried out in the LeClaire–Dow Instrumentation Facility at UMN.

References

- 1 C. Huber and G. Wächtershäuser, Activated Acetic Acid by Carbon Fixation on (Fe,Ni)S Under Primordial Conditions, *Science*, 1997, **276**(5310), 245–247, DOI: [10.1126/science.276.5310.245](https://doi.org/10.1126/science.276.5310.245).
- 2 C. Huber and G. Wächtershäuser, Peptides by Activation of Amino Acids with CO on (Ni,Fe)S Surfaces: Implications for the Origin of Life, *Science*, 1998, **281**(5377), 670–672, DOI: [10.1126/science.281.5377.670](https://doi.org/10.1126/science.281.5377.670).
- 3 K. Tanifuji and Y. Ohki, Metal–Sulfur Compounds in N₂ Reduction and Nitrogenase-Related Chemistry, *Chem. Rev.*, 2020, **120**(12), 5194–5251, DOI: [10.1021/acs.chemrev.9b00544](https://doi.org/10.1021/acs.chemrev.9b00544).
- 4 E. I. Solomon, D. E. Heppner, E. M. Johnston, J. W. Ginsbach, J. Cirera, M. Qayyum, M. T. Kieber-Emmons, C. H. Kjaergaard, R. G. Hadt and L. Tian, Copper Active Sites in Biology, *Chem. Rev.*, 2014, **114**(7), 3659–3853, DOI: [10.1021/cr400327t](https://doi.org/10.1021/cr400327t).
- 5 M. Can, F. A. Armstrong and S. W. Ragsdale, Structure, Function, and Mechanism of the Nickel Metalloenzymes, CO Dehydrogenase, and Acetyl-CoA Synthase, *Chem. Rev.*, 2014, **114**(8), 4149–4174, DOI: [10.1021/cr400461p](https://doi.org/10.1021/cr400461p).
- 6 J. T. Perryman and J. M. Velázquez, Design Principles for Multinary Metal Chalcogenides: Toward Programmable Reactivity in Energy Conversion, *Chem. Mater.*, 2021, **33**(18), 7133–7147, DOI: [10.1021/acs.chemmater.1c01983](https://doi.org/10.1021/acs.chemmater.1c01983).
- 7 M. Nath, H. Singh and A. Saxena, Progress of Transition Metal Chalcogenides as Efficient Electrocatalysts for Energy Conversion, *Curr. Opin. Electrochem.*, 2022, **34**, 100993, DOI: [10.1016/j.coelec.2022.100993](https://doi.org/10.1016/j.coelec.2022.100993).
- 8 M. A. Reynolds, Minireview on the Evolution of Tetrathiometalate Salts as Protean Building Blocks of Catalysts and Materials for the Energy Transition: Recent Advances and Future Perspectives, *Energy Fuels*, 2021, **35**(19), 15285–15300, DOI: [10.1021/acs.energyfuels.1c02039](https://doi.org/10.1021/acs.energyfuels.1c02039).
- 9 J. Kibsgaard, T. F. Jaramillo and F. Besenbacher, Building an Appropriate Active-Site Motif into a Hydrogen-Evolution Catalyst with Thiomolybdate [Mo₃S₁₃]²⁻ Clusters, *Nat. Chem.*, 2014, **6**(3), 248–253, DOI: [10.1038/nchem.1853](https://doi.org/10.1038/nchem.1853).
- 10 C. Dong, S. Nematulloev, P. Yuan and O. M. Bakr, Atomically Precise Copper Nanoclusters, in *Atomically Precise Nanochemistry*, 2023, pp. 257–283. DOI: [10.1002/9781119788676.ch8](https://doi.org/10.1002/9781119788676.ch8).
- 11 X. Liu and D. Astruc, Atomically Precise Copper Nanoclusters and Their Applications, *Coord. Chem. Rev.*, 2018, **359**, 112–126, DOI: [10.1016/j.ccr.2018.01.001](https://doi.org/10.1016/j.ccr.2018.01.001).

- 12 T. W. Hayton, Atomically Precise Nanoclusters of Iron, Cobalt, and Nickel, in *Atomically Precise Nanochemistry*, 2023, pp. 285–307. DOI: [10.1002/9781119788676.ch9](https://doi.org/10.1002/9781119788676.ch9).
- 13 R. Maity, B. S. Birenheide, F. Breher and B. Sarkar, Cooperative Effects in Multimetallic Complexes Applied in Catalysis, *ChemCatChem*, 2021, **13**(10), 2337–2370, DOI: [10.1002/cctc.202001951](https://doi.org/10.1002/cctc.202001951).
- 14 T. Jia, Y.-X. Li, X.-H. Ma, M.-M. Zhang, X.-Y. Dong, J. Ai and S.-Q. Zang, Atomically Precise Ultrasmall Copper Cluster for Room-Temperature Highly Regioselective Dehydrogenative Coupling, *Nat. Commun.*, 2023, **14**(1), 6877, DOI: [10.1038/s41467-023-42688-3](https://doi.org/10.1038/s41467-023-42688-3).
- 15 A. W. Beamer and J. A. Buss, Synthesis, Structural Characterization, and, CO₂ Reactivity of a Constitutionally Analogous Series of Tricopper Mono-, Di-, and Trihydrides, *J. Am. Chem. Soc.*, 2023, **145**(23), 12911–12919, DOI: [10.1021/jacs.3c04170](https://doi.org/10.1021/jacs.3c04170).
- 16 A. W. Cook, Z. R. Jones, G. Wu, S. L. Scott and T. W. Hayton, An Organometallic Cu₂₀ Nanocluster: Synthesis, Characterization, Immobilization on Silica, and “Click” Chemistry, *J. Am. Chem. Soc.*, 2018, **140**(1), 394–400, DOI: [10.1021/jacs.7b10960](https://doi.org/10.1021/jacs.7b10960).
- 17 B. S. Mitchell, A. Chirila, J. A. Kephart, A. C. Boggiano, S. M. Krajewski, D. Rogers, W. Kaminsky and A. Velian, Metal–Support Interactions in Molecular Single-Site Cluster Catalysts, *J. Am. Chem. Soc.*, 2022, **144**(40), 18459–18469, DOI: [10.1021/jacs.2c07033](https://doi.org/10.1021/jacs.2c07033).
- 18 L. N. V. Le, J. P. Joyce, P. H. Oyala, S. DeBeer and T. Agapie, Highly Activated Terminal Carbon Monoxide Ligand in an Iron–Sulfur Cluster Model of FeMco with Intermediate Local Spin State at Fe, *J. Am. Chem. Soc.*, 2024, **146**(8), 5045–5050, DOI: [10.1021/jacs.3c12025](https://doi.org/10.1021/jacs.3c12025).
- 19 A. G. Scott, D. Alves Galico, I. Bogacz, P. H. Oyala, J. Yano, E. A. Sutura, M. Murugesu and T. Agapie, High-Spin and Reactive Fe₁₃ Cluster with Exposed Metal Sites, *Angew. Chem., Int. Ed.*, 2023, **62**(49), e202313880, DOI: [10.1002/anie.202313880](https://doi.org/10.1002/anie.202313880).
- 20 C. E. Juda, R. Handford, A. K. Bartholomew, T. Powers, N. X. Gu, E. Meyers, N. Roth, Y.-S. Chen, S.-L. Zheng and T. Betley, Cluster Dynamics of Heterometallic Trinuclear Clusters during Ligand Substitution, Redox Chemistry, and Group Transfer Processes, *Chem. Sci.*, 2024, **15**, 8242–8248, DOI: [10.1039/D3SC03606E](https://doi.org/10.1039/D3SC03606E).
- 21 A. A. Fertig, W. W. Brennessel, J. R. McKone and E. M. Matson, Concerted Multiproton–Multielectron Transfer for the Reduction of O₂ to H₂O with a Polyoxovanadate Cluster, *J. Am. Chem. Soc.*, 2021, **143**(38), 15756–15768, DOI: [10.1021/jacs.1c07076](https://doi.org/10.1021/jacs.1c07076).
- 22 A. C. Brown, N. B. Thompson and D. L. M. Suess, Evidence for Low-Valent Electronic Configurations in Iron–Sulfur Clusters, *J. Am. Chem. Soc.*, 2022, **144**(20), 9066–9073, DOI: [10.1021/jacs.2c01872](https://doi.org/10.1021/jacs.2c01872).
- 23 S. C. Rathnayaka, S. M. Islam, I. M. DiMucci, S. N. MacMillan, K. M. Lancaster and N. P. Mankad, Probing the Electronic and Mechanistic Roles of the u⁴-Sulfur Atom in a Synthetic CuZ Model System, *Chem. Sci.*, 2020, **11**(13), 3441–3447, DOI: [10.1039/C9SC06251C](https://doi.org/10.1039/C9SC06251C).
- 24 S. Pattanayak and L. A. Berben, Pre-Equilibrium Reaction Mechanism as a Strategy to Enhance Rate and Lower Overpotential in Electrocatalysis, *J. Am. Chem. Soc.*, 2023, **145**(6), 3419–3426, DOI: [10.1021/jacs.2c10942](https://doi.org/10.1021/jacs.2c10942).
- 25 M. C. Eaton, V. J. Catalano, J. Shearer and L. J. Murray, Dinitrogen Insertion and Cleavage by a Metal–Metal Bonded Tricobalt(i) Cluster, *J. Am. Chem. Soc.*, 2021, **143**(15), 5649–5653, DOI: [10.1021/jacs.1c01840](https://doi.org/10.1021/jacs.1c01840).
- 26 S. Zhao, N. Austin, M. Li, Y. Song, S. D. House, S. Bernhard, J. C. Yang, G. Mpourmpakis and R. Jin, Influence of Atomic-Level Morphology on Catalysis: The Case of Sphere and Rod-Like Gold Nanoclusters for CO₂ Electroreduction, *ACS Catal.*, 2018, **8**(6), 4996–5001, DOI: [10.1021/acscatal.8b00365](https://doi.org/10.1021/acscatal.8b00365).
- 27 S. Li, X. Du, Z. Liu, Y. Li, Y. Shao and R. Jin, Size Effects of Atomically Precise Gold Nanoclusters in Catalysis, *Precis. Chem.*, 2023, **1**(1), 14–28, DOI: [10.1021/prechem.3c00008](https://doi.org/10.1021/prechem.3c00008).
- 28 L.-J. Liu, Z.-Y. Wang, Z.-Y. Wang, R. Wang, S.-Q. Zang and T. C. W. Mak, Mediating CO₂ Electroreduction Activity and Selectivity over Atomically Precise Copper Clusters, *Angew. Chem., Int. Ed.*, 2022, **61**(35), e202205626, DOI: [10.1002/anie.202205626](https://doi.org/10.1002/anie.202205626).
- 29 Z. Huang, W. Luo, L. Ma, M. Yu, X. Ren, M. He, S. Polen, K. Click, B. Garrett, J. Lu, K. Amine, C. Hadad, W. Chen, A. Asthagiri and Y. Wu, Dimeric [Mo₂S₁₂]²⁻ Cluster: A Molecular Analogue of MoS₂ Edges for Superior Hydrogen-Evolution Electrocatalysis, *Angew. Chem., Int. Ed.*, 2015, **54**(50), 15181–15185, DOI: [10.1002/anie.201507529](https://doi.org/10.1002/anie.201507529).
- 30 J.-P. Dong, Y. Xu, X.-G. Zhang, H. Zhang, L. Yao, R. Wang and S.-Q. Zang, Copper-Sulfur-Nitrogen Cluster Providing a Local Proton for Efficient Carbon Dioxide Photoreduction, *Angew. Chem., Int. Ed.*, 2023, **62**(48), e202313648, DOI: [10.1002/anie.202313648](https://doi.org/10.1002/anie.202313648).
- 31 M. R. DuBois, Catalytic Applications of Transition-Metal Complexes with Sulfide Ligands, *Chem. Rev.*, 1989, **89**(1), 1–9, DOI: [10.1021/cr00091a001](https://doi.org/10.1021/cr00091a001).
- 32 S. C. Lee, W. Lo and R. H. Holm, Developments in the Biomimetic Chemistry of Cubane-Type and Higher Nuclearity Iron–Sulfur Clusters, *Chem. Rev.*, 2014, **114**(7), 3579–3600, DOI: [10.1021/cr4004067](https://doi.org/10.1021/cr4004067).
- 33 Y. Ohki, K. Uchida, M. Tada, R. E. Cramer, T. Ogura and T. Ohta, N₂ Activation on a Molybdenum–Titanium–Sulfur Cluster, *Nat. Commun.*, 2018, **9**(1), 3200, DOI: [10.1038/s41467-018-05630-6](https://doi.org/10.1038/s41467-018-05630-6).
- 34 J. A. Kephart, B. S. Mitchell, A. Chirila, K. J. Anderton, D. Rogers, W. Kaminsky and A. Velian, Atomically Defined Nanopropeller Fe₃Co₆Se₈(Ph₂PNTol)₆: Functional Model for the Electronic Metal–Support Interaction Effect and High Catalytic Activity for Carbodiimide Formation, *J. Am. Chem. Soc.*, 2019, **141**(50), 19605–19610, DOI: [10.1021/jacs.9b12473](https://doi.org/10.1021/jacs.9b12473).
- 35 A. L. Gushchin, Y. A. Laricheva, M. N. Sokolov and R. Llusar, Tri- and Tetranuclear Molybdenum and Tungsten Chalcogenide Clusters: On the Way to New

- Materials and Catalysts *, *Russ. Chem. Rev.*, 2018, **87**(7), 670, DOI: [10.1070/RCR4800](https://doi.org/10.1070/RCR4800).
- 36 S. Shitaya, K. Nomura and A. Inagaki, Light-Driven Catalytic Hydrogenation of Carbon Dioxide at Low-Pressure by a Trinuclear Iridium Polyhydride Complex, *Chem. Commun.*, 2019, **55**(35), 5087–5090, DOI: [10.1039/C9CC00916G](https://doi.org/10.1039/C9CC00916G).
- 37 Y. Ohki, K. Munakata, Y. Matsuoka, R. Hara, M. Kachi, K. Uchida, M. Tada, R. E. Cramer, W. M. C. Sameera, T. Takayama, Y. Sakai, S. Kuriyama, Y. Nishibayashi and K. Tanifuji, Nitrogen Reduction by the Fe Sites of Synthetic [Mo₃S₄Fe] Cubes, *Nature*, 2022, **607**(7917), 86–90, DOI: [10.1038/s41586-022-04848-1](https://doi.org/10.1038/s41586-022-04848-1).
- 38 K. Patra, W. W. Brennessel and E. M. Matson, Molybdenum Sulphide Clusters as Redox-Active Supports for Low-Valent Uranium, *Chem. Commun.*, 2024, **60**(5), 530–533, DOI: [10.1039/D3CC05561B](https://doi.org/10.1039/D3CC05561B).
- 39 M. V. L. Ocampo and L. J. Murray, Metal-Tuned Ligand Reactivity Enables CX₂ (X = O, S) Homocoupling with Spectator Cu Centers, *J. Am. Chem. Soc.*, 2024, **146**(1), 1019–1025, DOI: [10.1021/jacs.3c11928](https://doi.org/10.1021/jacs.3c11928).
- 40 B. J. Johnson, W. E. Antholine, S. V. Lindeman, M. J. Graham and N. P. Mankad, A One-Hole Cu₄S Cluster with N₂O Reductase Activity: A Structural and Functional Model for CuZ*, *J. Am. Chem. Soc.*, 2016, **138**(40), 13107–13110, DOI: [10.1021/jacs.6b05480](https://doi.org/10.1021/jacs.6b05480).
- 41 C.-W. Hsu, S. C. Rathnayaka, S. M. Islam, S. N. MacMillan and N. P. Mankad, N₂O Reductase Activity of a [Cu₄S] Cluster in the 4CuI Redox State Modulated by Hydrogen Bond Donors and Proton Relays in the Secondary Coordination Sphere, *Angew. Chem., Int. Ed.*, 2020, **59**(2), 627–631, DOI: [10.1002/anie.201906327](https://doi.org/10.1002/anie.201906327).
- 42 N. P. Mankad, Triazenide-Supported [Cu₄S] Structural Mimics of CuZ That Mediate N₂O Disproportionation Rather than Reduction, *Chem. Sci.*, 2024, **15**(5), 1820–1828, DOI: [10.1039/D3SC05451A](https://doi.org/10.1039/D3SC05451A).
- 43 Y. Chen, K. Chen, J. Fu, A. Yamaguchi, H. Li, H. Pan, J. Hu, M. Miyauchi and M. Liu, Recent Advances in the Utilization of Copper Sulfide Compounds for Electrochemical CO₂ Reduction, *Nano Mater. Sci.*, 2020, **2**(3), 235–247, DOI: [10.1016/j.nanoms.2019.10.006](https://doi.org/10.1016/j.nanoms.2019.10.006).
- 44 T.-T. Zhuang, Z.-Q. Liang, A. Seifitokaldani, Y. Li, P. De Luna, T. Burdyny, F. Che, F. Meng, Y. Min, R. Quintero-Bermudez, C. T. Dinh, Y. Pang, M. Zhong, B. Zhang, J. Li, P.-N. Chen, X.-L. Zheng, H. Liang, W.-N. Ge, B.-J. Ye, D. Sinton, S.-H. Yu and E. H. Sargent, Steering Post-C–C Coupling Selectivity Enables High Efficiency Electroreduction of Carbon Dioxide to Multi-Carbon Alcohols, *Nat. Catal.*, 2018, **1**(6), 421–428, DOI: [10.1038/s41929-018-0084-7](https://doi.org/10.1038/s41929-018-0084-7).
- 45 A. Saxena, W. Liyanage, J. Masud, S. Kapila and M. Nath, Selective Electroreduction of CO₂ to Carbon-Rich Products with a Simple Binary Copper Selenide Electrocatalyst, *J. Mater. Chem. A*, 2021, **9**(11), 7150–7161, DOI: [10.1039/D0TA11518E](https://doi.org/10.1039/D0TA11518E).
- 46 T. Shinagawa, G. O. Larrazábal, A. J. Martín, F. Krumeich and J. Pérez-Ramírez, Sulfur-Modified Copper Catalysts for the Electrochemical Reduction of Carbon Dioxide to Formate, *ACS Catal.*, 2018, **8**(2), 837–844, DOI: [10.1021/acscatal.7b03161](https://doi.org/10.1021/acscatal.7b03161).
- 47 P. Kar, S. Farsinezhad, X. Zhang and K. Shankar, Anodic Cu₂S and CuS Nanorod and Nanowall Arrays: Preparation, Properties and Application in CO₂ Photoreduction, *Nanoscale*, 2014, **6**(23), 14305–14318, DOI: [10.1039/C4NR05371K](https://doi.org/10.1039/C4NR05371K).
- 48 Z. Zhao, X. Peng, X. Liu, X. Sun, J. Shi, L. Han, G. Li and J. Luo, Efficient and Stable Electroreduction of CO₂ to CH₄ on CuS Nanosheet Arrays, *J. Mater. Chem. A*, 2017, **5**(38), 20239–20243, DOI: [10.1039/C7TA05507B](https://doi.org/10.1039/C7TA05507B).
- 49 K. R. Phillips, Y. Katayama, J. Hwang and Y. Shao-Horn, Sulfide-Derived Copper for Electrochemical Conversion of CO₂ to Formic Acid, *J. Phys. Chem. Lett.*, 2018, **9**(15), 4407–4412, DOI: [10.1021/acs.jpcclett.8b01601](https://doi.org/10.1021/acs.jpcclett.8b01601).
- 50 Y. Huang, Y. Deng, A. D. Handoko, G. K. L. Goh and B. S. Yeo, Rational Design of Sulfur-Doped Copper Catalysts for the Selective Electroreduction of Carbon Dioxide to Formate, *ChemSusChem*, 2018, **11**(1), 320–326, DOI: [10.1002/cssc.201701314](https://doi.org/10.1002/cssc.201701314).
- 51 C. Peng, G. Luo, J. Zhang, M. Chen, Z. Wang, T.-K. Sham, L. Zhang, Y. Li and G. Zheng, Double Sulfur Vacancies by Lithium Tuning Enhance CO₂ Electroreduction to n-Propanol, *Nat. Commun.*, 2021, **12**(1), 1580, DOI: [10.1038/s41467-021-21901-1](https://doi.org/10.1038/s41467-021-21901-1).
- 52 Y. Deng, Y. Huang, D. Ren, A. D. Handoko, Z. W. Seh, P. Hirunsit and B. S. Yeo, On the Role of Sulfur for the Selective Electrochemical Reduction of CO₂ to Formate on Cu_xS Catalysts, *ACS Appl. Mater. Interfaces*, 2018, **10**(34), 28572–28581, DOI: [10.1021/acsami.8b08428](https://doi.org/10.1021/acsami.8b08428).
- 53 R. García-Muelas, F. Dattila, T. Shinagawa, A. J. Martín, J. Pérez-Ramírez and N. López, Origin of the Selective Electroreduction of Carbon Dioxide to Formate by Chalcogen Modified Copper, *J. Phys. Chem. Lett.*, 2018, **9**(24), 7153–7159, DOI: [10.1021/acs.jpcclett.8b03212](https://doi.org/10.1021/acs.jpcclett.8b03212).
- 54 S. Dehnen, A. Eichhöfer and D. Fenske, Chalcogen-Bridged Copper Clusters, *Eur. J. Inorg. Chem.*, 2002, **2002**(2), 279–317, DOI: [10.1002/1099-0682\(20022\)2002:2<279::AID-EJIC279>3.0.CO;2-H](https://doi.org/10.1002/1099-0682(20022)2002:2<279::AID-EJIC279>3.0.CO;2-H).
- 55 O. Fuhr, S. Dehnen and D. Fenske, Chalcogenide Clusters of Copper and Silver from Silylated Chalcogenide Sources, *Chem. Soc. Rev.*, 2013, **42**(4), 1871–1906, DOI: [10.1039/C2CS35252D](https://doi.org/10.1039/C2CS35252D).
- 56 J. F. Corrigan, O. Fuhr and D. Fenske, Metal Chalcogenide Clusters on the Border between Molecules and Materials, *Adv. Mater.*, 2009, **21**(18), 1867–1871, DOI: [10.1002/adma.200802897](https://doi.org/10.1002/adma.200802897).
- 57 S. Dehnen, A. Schäfer, D. Fenske and R. Ahlrichs, New Sulfur- and Selenium-Bridged Copper Clusters; Ab Initio Calculations on [Cu_{2n}Se_n(PH₃)_m] Clusters, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**(7), 746–749, DOI: [10.1002/anie.199407461](https://doi.org/10.1002/anie.199407461).
- 58 C. B. Khadka, B. K. Najafabadi, M. Hesari, M. S. Workentin and J. F. Corrigan, Copper Chalcogenide Clusters Stabilized with Ferrocene-Based Diphosphine Ligands, *Inorg. Chem.*, 2013, **52**(12), 6798–6805, DOI: [10.1021/ic3021854](https://doi.org/10.1021/ic3021854).

- 59 X.-X. Yang, I. Issac, S. Lebedkin, M. Kühn, F. Weigend, D. Fenske, O. Fuhr and A. Eichhöfer, Red-Luminescent Biphosphine Stabilized 'Cu₁₂S₆' Cluster Molecules, *Chem. Commun.*, 2014, **50**(75), 11043–11045, DOI: [10.1039/C4CC04702H](https://doi.org/10.1039/C4CC04702H).
- 60 A. M. Polgar, F. Weigend, A. Zhang, M. J. Stillman and J. F. Corrigan, A N-Heterocyclic Carbene-Stabilized Coinage Metal-Chalcogenide Framework with Tunable Optical Properties, *J. Am. Chem. Soc.*, 2017, **139**(40), 14045–14048, DOI: [10.1021/jacs.7b09025](https://doi.org/10.1021/jacs.7b09025).
- 61 A. Eichhöfer, G. Buth, S. Lebedkin, M. Kühn and F. Weigend, Luminescence in Phosphine-Stabilized Copper Chalcogenide Cluster Molecules—A Comparative Study, *Inorg. Chem.*, 2015, **54**(19), 9413–9422, DOI: [10.1021/acs.inorgchem.5b01146](https://doi.org/10.1021/acs.inorgchem.5b01146).
- 62 O. Veselska and A. Demessence, d¹⁰ Coinage Metal Organic Chalcogenolates: From Oligomers to Coordination Polymers, *Coord. Chem. Rev.*, 2018, **355**, 240–270, DOI: [10.1016/j.ccr.2017.08.014](https://doi.org/10.1016/j.ccr.2017.08.014).
- 63 M. Brookhart, M. L. H. Green and G. Parkin, Agostic Interactions in Transition Metal Compounds, *Proc. Natl. Acad. Sci. U. S. A.*, 2007, **104**(17), 6908–6914, DOI: [10.1073/pnas.0610747104](https://doi.org/10.1073/pnas.0610747104).
- 64 H. A. Fargher, T. J. Sherbow, M. M. Haley, D. W. Johnson and M. D. Pluth, C–H...S Hydrogen Bonding Interactions, *Chem. Soc. Rev.*, 2022, **51**(4), 1454–1469, DOI: [10.1039/D1CS00838B](https://doi.org/10.1039/D1CS00838B).
- 65 Y. Liu, S. Chatterjee, G. E. Cutsail III, S. Peredkov, S. K. Gupta, S. Dechert, S. DeBeer and F. Meyer, Cu₄S Cluster in “0-Hole” and “1-Hole” States: Geometric and Electronic Structure Variations for the Active Cu_Z* Site of N₂O Reductase, *J. Am. Chem. Soc.*, 2023, **145**, 18477–18486, DOI: [10.1021/jacs.3c04893](https://doi.org/10.1021/jacs.3c04893).
- 66 M. S. Eberhart, J. R. Norton, A. Zuzek, W. Sattler and S. Rucolo, Electron Transfer from Hexameric Copper Hydrides, *J. Am. Chem. Soc.*, 2013, **135**(46), 17262–17265, DOI: [10.1021/ja408925m](https://doi.org/10.1021/ja408925m).
- 67 S. Liu, M. S. Eberhart, J. R. Norton, X. Yin, M. C. Neary and D. W. Paley, Cationic Copper Hydride Clusters Arising from Oxidation of (Ph₃P)₆Cu₆H₆, *J. Am. Chem. Soc.*, 2017, **139**(23), 7685–7688, DOI: [10.1021/jacs.7b02183](https://doi.org/10.1021/jacs.7b02183).
- 68 L. Grunwald, M. Clémancey, D. Klose, L. Dubois, S. Gambarelli, G. Jeschke, M. Wörle, G. Blondin and V. Mougel, A Complete Biomimetic Iron-Sulfur Cubane Redox Series, *Proc. Natl. Acad. Sci. U. S. A.*, 2022, **119**(31), e2122677119, DOI: [10.1073/pnas.2122677119](https://doi.org/10.1073/pnas.2122677119).
- 69 G. Moula, T. Matsumoto, M. E. Miehlich, K. Meyer and K. Tatsumi, Synthesis of an All-Ferric Cuboidal Iron-Sulfur Cluster [Fe₄S₄(SAR)₄], *Angew. Chem., Int. Ed.*, 2018, **57**(36), 11594–11597, DOI: [10.1002/anie.201803679](https://doi.org/10.1002/anie.201803679).