

Cite this: *Nanoscale Horiz.*, 2023,
8, 63Received 30th September 2022,
Accepted 11th November 2022

DOI: 10.1039/d2nh00457g

rsc.li/nanoscale-horizons

Cu and Si co-doping on TiO₂ nanosheets to modulate reactive oxygen species for efficient photocatalytic methane conversion†

Jun Ma,^{ab} Jingxiang Low,^{id}^a Di Wu,^a Wanbing Gong,^a Hengjie Liu,^{id}^a
Dong Liu,^{id}^{*ab} Ran Long,^{id}^{*a} and Yujie Xiong,^{id}^{*a}

In this study, we successfully construct Cu and Si co-doped ultrathin TiO₂ nanosheets. As confirmed by comprehensive characterizations, Cu and Si co-doping can rationally tailor the electronic structure of TiO₂ to maneuver reactive oxygen species for effective photocatalytic methane conversion. In addition, this co-doping greatly enhances the utilization efficiency of photogenerated charges. Furthermore, it is revealed that Cu and Si co-doping can significantly boost the adsorption and activation of methane on TiO₂ nanosheets. As a result, the optimized catalyst achieves a C₂H₆ production rate of 33.8 μmol g⁻¹ h⁻¹ with a selectivity of 88.4%. This work provides insights into nanocatalyst design toward efficient photocatalytic methane conversion into value-added compounds.

1. Introduction

With the rapid development of exploration and exploitation technology, natural gas reserves and production have been continuously growing over decades.^{1–4} Methane has received tremendous attention from both scientific and industrial communities due to its abundance and potential as a feedstock for manufacturing high-value fuels and chemicals.^{5,6} However, the inert C–H bond and highly symmetrical structure of methane molecule make it substantially challenging to transform methane into target products. Conventional methane activation is a severe energy-intensive process with carbon emissions. It requires critical conditions (*i.e.*, high temperature and

New concepts

Methane (CH₄), the predominant constituent of natural gas, shale gas and combustible ice, has provoked increasing attention as an essential feedstock for energy supply and chemical production. However, current industrial routes for methane transformation are highly energy-intensive. Less than 10% of the global methane production is used for chemical manufacture, which mainly ascribes to the inert C–H bond and highly symmetrical structure of methane molecule. Herein, we provide an efficient and selective candidate for photocatalytic methane conversion into ethane through Cu and Si co-doping into ultrathin TiO₂ nanosheets. As determined by comprehensive spectroscopic characterizations, the presence of Cu and Si could rationally regulate the electronic structure to modulate reactive oxygen species for C–H bond activation of methane molecule. Impressively, the as-synthesized catalyst possesses a remarkable catalytic activity and selectivity with a 33.8 μmol g⁻¹ h⁻¹ C₂H₆ generation rate and 88.4% C₂H₆ selectivity at room temperature under light irradiation. This co-doping approach provides a feasible route for designing low-cost and highly active photocatalysts for practical methane conversion applications under mild conditions.

pressure) to activate the C–H bond combined with sophisticated post-processes.^{7–9} Thus, it is urgent to develop efficient and selective approaches for the transformation of methane into value-added compounds under moderate conditions.

Recently, photocatalysis emerges as a prospective approach for methane conversion under mild conditions because it can utilize reactive oxygen species (ROS) to dissociate the C–H bond of methane upon photoexcitation, and greatly decrease the energy barrier of C–H bond activation.^{1,2,10–12} In 1998, direct photocatalytic methane coupling was first achieved over SiO₂–Al₂O₃–TiO₂ ternary catalyst.¹³ Since then, various semiconductors-based photocatalysts have been employed for catalytic coupling of methane into ethane at room temperature.^{1,14,15} Among these photocatalysts, TiO₂-based catalysts are one of the most widely applied materials for photocatalytic methane conversion due to their suitable energy band structure and malleable qualities.^{16–18} For example, Tang and co-workers constructed Pt and CuO_x co-decorated TiO₂ for the

^a Hefei National Research Center for Physical Sciences at the Microscale, School of Chemistry and Materials Science, National Synchrotron Radiation Laboratory, School of Nuclear Science and Technology, University of Science and Technology of China, Hefei, Anhui 230026, China. E-mail: dongliu@ustc.edu.cn, longran@ustc.edu.cn, yjxiong@ustc.edu.cn

^b Suzhou Institute for Advanced Research, University of Science and Technology of China, Suzhou, Jiangsu 215123, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2nh00457g>

photocatalytic oxidative coupling of methane (OCM), which achieved a $6.8 \mu\text{mol h}^{-1}$ yield of C_{2+} products (C_2H_6 and C_2H_4) with approximately 60% selectivity.¹⁹ Despite these advances, the efficiency and selectivity of photocatalytic methane conversion are still unsatisfactory due to scarce surface active sites. Therefore, efficient and selective photocatalysts should be further developed to satisfy the requirements for practical applications.

Copper (Cu) is generally regarded as the active center of particulate methane monooxygenases enzyme in the nature while silica matrix can improve the photocatalytic stability.^{20–22} Here, we successfully fabricated Cu and Si co-doped ultrathin TiO_2 nanosheets for efficient photocatalytic methane conversion at room temperature and ambient pressure. As demonstrated by comprehensive characterizations, the presence of Cu and Si could rationally regulate the electronic structure of TiO_2 nanosheets and modulate the reactive oxygen species for the activation of C–H bonds, accompanied with the presence of oxygen vacancies and Ti^{3+} species in the TiO_2 matrix. Furthermore, this co-doping could substantially improve the separation and migration of the photogenerated charges. As a result, the optimized catalyst achieves a C_2H_6 production rate of $33.8 \mu\text{mol g}^{-1} \text{h}^{-1}$ with a selectivity of 88.4% at room temperature.

2. Results and discussion

The Cu and Si co-doped ultrathin TiO_2 nanosheets were synthesized through a simple solvothermal method in ethanol solution (shown in Fig. 1) using $\text{Cu}(\text{NO}_3)_2$ and tetraethyl orthosilicate (TEOS) as doping precursors, respectively. The as-synthesized samples are denoted as $\text{TiO}_2(\text{Si})\text{-}X\%\text{Cu}$, where X is the molar percentage of Cu atoms in the precursors. The crystal structures of TiO_2 based catalysts were identified using powder X-ray diffraction (XRD) characterization. As shown in Fig. S1 (ESI[†]), the XRD patterns of all $\text{TiO}_2(\text{Si})\text{-}X\%\text{Cu}$ nanosheets are attributed to anatase TiO_2 (JCPDS-21-1272), without any secondary patterns related to Cu/Si or its oxide phases, suggesting that co-doping does not alter the crystal structure of TiO_2 nanosheets. As evidenced by the transmission electron microscopy (TEM) characterization (Fig. 1b and Fig. S2, ESI[†]), the ultrathin TiO_2 nanosheets display a lateral sheet size of *ca.* 10 nm and a thickness of *ca.* 3 nm, exposing abundant sites for photocatalytic reactions. The high-resolution TEM (HRTEM) image (Fig. 1c) shows lattice fringes of 0.19 nm and 0.20 nm, indexing to the (200) and (020) facets of anatase TiO_2 , respectively. These results reveal that the as-synthesized ultrathin TiO_2 nanosheets exhibit a high ratio of reactive (001) faces.^{23,24} The element distribution of the co-doped TiO_2 nanosheets is then analysed by energy-dispersive X-ray spectroscopy (EDS). As shown in Fig. 1d, the homogeneous distribution of Ti, O, Cu, and Si elements is confirmed throughout the nanosheets. Combined with the XRD results, this indicates that Cu and Si were successfully and uniformly doped into TiO_2 .²⁵ Furthermore, UV-vis diffuse reflectance spectroscopy (Fig. 1e) revealed that the absorption edges of the TiO_2 nanosheets redshift



Fig. 1 (a) Schematic illustration of the preparation of Cu & Si co-doped ultrathin TiO_2 nanosheets. (b) TEM, (c) HRTEM images and (d) EDS mapping of $\text{TiO}_2(\text{Si})\text{-}1\%\text{Cu}$ nanosheets. (e) UV-vis diffuse reflectance spectra of the prepared Cu & Si co-doped TiO_2 nanosheets.

with the incorporation of Cu due to the presence of oxygen vacancies and $2E_g \rightarrow 2T_{2g}$ transitions from O to Cu atoms,²³ while the absorption edges of TiO_2 show negligible relevance to Si doping. Interestingly, Cu doping could increase the near-infrared absorption up to 800 nm, assigned to the d–d transitions of doped Cu,^{23,25,26} which would obviously enhance the light absorption for the photocatalytic reaction. In addition, the absorption in the near-infrared region can increase the surface temperature of the photocatalyst due to photothermal effect (Fig. S3, ESI[†]), facilitating methane activation on the TiO_2 surface.

X-ray photoelectron spectroscopy (XPS) was employed to further investigate the electronic structure of the co-doped TiO_2 nanosheets. The refined Cu 2p XPS spectra of $\text{TiO}_2\text{-}1\%\text{Cu}$ and $\text{TiO}_2(\text{Si})\text{-}1\%\text{Cu}$ (Fig. S4, ESI[†]) both exhibit a +2 oxidation state, confirmed by bimodal peaks at 933.2 eV (Cu $2p_{3/2}$) and 953.1 eV (Cu $2p_{1/2}$).²³ The Si 2p spectra of $\text{TiO}_2(\text{Si})$ and $\text{TiO}_2(\text{Si})\text{-}1\%\text{Cu}$ (Fig. S5, ESI[†]) are mainly attributed to +4 oxidation state.^{27,28} As shown in Fig. 2a, the majority of Ti is in the Ti^{4+} state for all samples, while Ti^{3+} can be distinctly observed in the Ti 2p spectra of $\text{TiO}_2\text{-}1\%\text{Cu}$ and $\text{TiO}_2(\text{Si})\text{-}1\%\text{Cu}$ due to the introduction of oxygen vacancies by Cu doping. Interestingly, the intensity of Ti^{3+} in the Ti 2p XPS spectrum decreased after the incorporation of Si into the TiO_2 nanosheets, which resulted from the modulation of the electronic structure between Si and Ti atoms.^{28,29} To further elucidate the oxidation states of the doped Cu, electron paramagnetic resonance (EPR) was performed to recognize the electronic structure and coordination environment of the dopant.³⁰ As shown in Fig. S6 (ESI[†]), the EPR spectra of $\text{TiO}_2\text{-}1\%\text{Cu}$ and

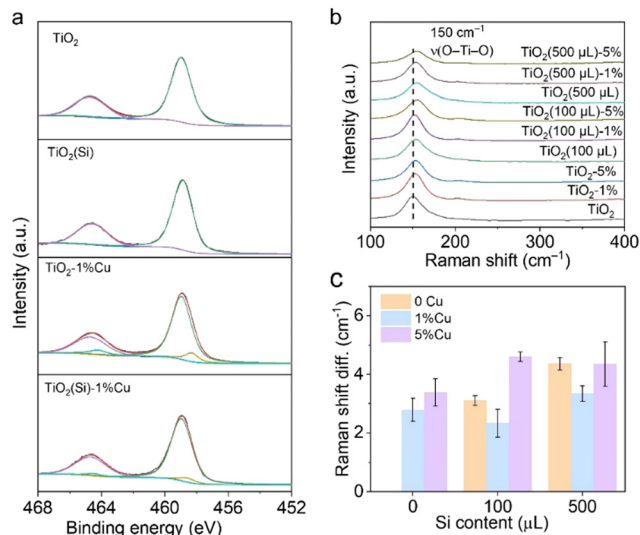


Fig. 2 (a) Ti 2p XPS spectra and (b) Raman spectra of $\text{TiO}_2(\text{Si})-X\%\text{Cu}$ nanosheets. (c) Raman shift difference of $\text{TiO}_2(\text{Si})-X\%\text{Cu}$ nanosheets compared with TiO_2 nanosheets.

$\text{TiO}_2(\text{Si})-1\%\text{Cu}$ exhibit a characteristic Cu^{2+} hyperfine signal with resonance parameters at $g_{\parallel} = 2.33$ and $g_{\perp} = 2.07$, which indicates that Cu^{2+} ions substitute Ti sites in the TiO_2 lattice.^{30,31}

Moreover, Raman spectroscopy was carried out to investigate the local structure alteration upon the incorporation of Cu and Si. As shown in Fig. 2b, the Raman spectra exhibit intensive peaks at 149 cm^{-1} attributed to the E_g mode of anatase TiO_2 , consistent with the XRD results.^{25,32} The E_g mode, assigned to the symmetric stretching vibration of O-Ti-O in TiO_2 ,³² shifts towards a higher wavenumber upon the incorporation of Cu or Si. This phenomenon could occur due to the introduction of Cu and Si induces lattice distortion in TiO_2 and the formation of Cu-O-Ti or Si-O-Ti bonds.^{25,32} The lattice distortion could maneuver the adsorption configuration of reactant molecules on the surface.^{25,33} In particular, the peak shift achieves its smallest when 1% molar Cu and 100 μL Si are doped into TiO_2 nanosheets (Fig. 2c), originating from the distortion balance between Cu and Si,³⁴ which may boost the photocatalytic activity and stability over the co-doped TiO_2 .

To clarify the co-doping effect on photocatalytic reactivity of TiO_2 , *in situ* EPR was carried out to detect the ROS generated on the prepared TiO_2 nanosheets under light irradiation using 5, 5-dimethyl-1-pyrroline *N*-oxide (DMPO) as a spin-trapping agent. As revealed in Fig. 3a, the EPR spectra for TiO_2 and $\text{TiO}_2(\text{Si})$ nanosheets show quartet signals with an intensity ratio of 1 : 2 : 2 : 1, which could be assigned to the adduct of hydroxyl radicals with spin-trapping agent (DMPO- $\cdot\text{OH}$), while the EPR spectrum for $\text{TiO}_2-1\%\text{Cu}$ exhibits negligible DMPO- $\cdot\text{OH}$ signals. In contrast, a sextet signal is generated in the EPR spectra for $\text{TiO}_2(\text{Si})-1\%\text{Cu}$, which may result from the N-C bond cleavage and ring opening of DMPO over $\text{TiO}_2(\text{Si})-1\%\text{Cu}$ under light irradiation,^{35,36} indicating the significant oxidation ability of the co-doped TiO_2 . The EPR results demonstrate that the



Fig. 3 (a) *In situ* EPR spectra for the prepared TiO_2 nanosheets under irradiation using DMPO as a spinning trapping agent. (b) Photocatalytic performance of the prepared TiO_2 nanosheets after 4 h of light irradiation. (c) Mass spectra of ethane produced over $\text{TiO}_2(\text{Si})-1\%\text{Cu}$ using CH_4 and CD_4 as the feed gas. (d) Photocatalytic production rate in the cyclic test of $\text{TiO}_2(\text{Si})-1\%\text{Cu}$.

incorporation of Cu and Si can rationally modulate the oxidation capability of TiO_2 and the ROS for photocatalytic reactions, benefiting from the alteration of the electronic structure of TiO_2 and the presence of Ti^{3+} and oxygen vacancies.

Upon recognizing the status of doped Cu and Si in TiO_2 nanosheets, we are now in a position to evaluate the performance of the prepared TiO_2 nanosheets for photocatalytic methane conversion. The photocatalytic experiments were carried out in CH_4 saturated water under 300 W xenon lamp (PLS-SXE300, Perfect Light) irradiation under ambient conditions, where the solvation effect of H_2O could facilitate the desorption of products from the surface of the catalyst to avoid overoxidation.^{37,38} As detected by gas chromatography (GC, Agilent 7890B), the pure TiO_2 nanosheets are inactive for methane conversion (shown in Fig. 3b and Fig. S7, ESI[†]). Interestingly, the introduction of Cu or Si into the TiO_2 nanosheets endow the distinctly enhanced activity for methane conversion. Moreover, the synergistic effect of Cu and Si would further facilitate photocatalytic methane conversion over TiO_2 nanosheets. In particular, $\text{TiO}_2(100\mu\text{L Si})-1\%\text{Cu}$ achieves a C_2H_6 production rate of $33.8\ \mu\text{mol g}^{-1}\text{ h}^{-1}$ with a selectivity of 88.4% upon 4 h light irradiation, consistent with the Raman and *in situ* EPR characterizations. These results clearly demonstrate the importance of the ROS and the regulation of electronic structure in photocatalytic methane conversion. Nevertheless, the photocatalytic performance of the prepared catalyst declines with further increase in Cu or Si content, due to the shielding effect and photogenerated charge recombination.

To further elucidate the accuracy of the photocatalytic results, isotope labelling experiments are performed using CH_4 or CD_4 as the feed gas to conduct photocatalytic methane conversion over $\text{TiO}_2(\text{Si})-1\%\text{Cu}$. As shown in Fig. 3c, the m/z

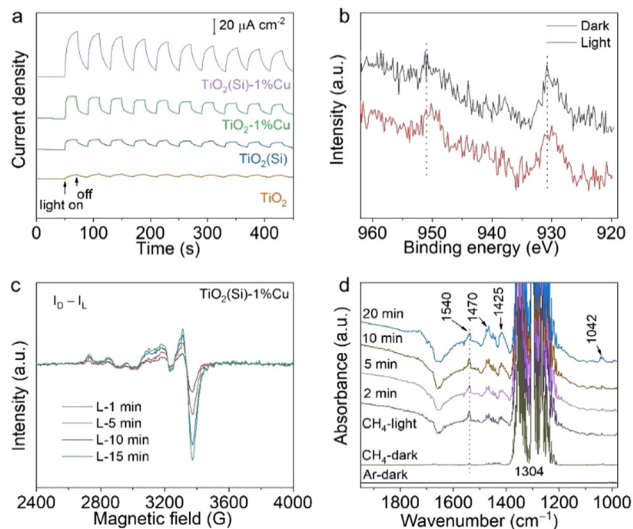


Fig. 4 (a) Transient photocurrent response of the prepared TiO_2 nanosheets. (b) The light-irradiated Cu 2p XPS spectra for $\text{TiO}_2(\text{Si})-1\% \text{Cu}$. (c) The EPR difference spectra between light irradiated spectra and pristine spectrum for $\text{TiO}_2(\text{Si})-1\% \text{Cu}$. (d) *In situ* DRIFTS spectra for photocatalytic methane conversion over $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ under light irradiation.

values of ethane vary upon changing the reactant gas. In detail, the location of the strongest peak shifts from $m/z = 28$ (using CH_4 feed gas) to $m/z = 32$ (using CD_4 as feed gas), and a new peak with constant relative intensity at $m/z = 36$ appears, demonstrating the produced ethane originating from the fed CH_4 . Moreover, control experiments showed that no products could be detected in the absence of methane, photocatalyst, or light irradiation (Fig. S8, ESI[†]), suggesting that the products originate from photocatalytic methane conversion over co-doped TiO_2 nanosheets. Moreover, the co-doped TiO_2 nanosheets exhibit significant photocatalytic stability, and the photocatalytic performance of $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ is well maintained for five cycles with each run of 4 h (Fig. 3d and Fig. S9, ESI[†]).

To comprehend the utilization efficiency of photogenerated charge carriers by co-doping, we performed photoelectrochemical measurements to observe the interfacial charge kinetics of TiO_2 nanosheets through the transient photocurrent response. As shown in Fig. 4a, the photocurrents of $\text{TiO}_2(\text{Si})$, $\text{TiO}_2-1\% \text{Cu}$ and $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ are obviously larger than that of pristine TiO_2 . More importantly, $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ achieves the highest transient photocurrent, indicating that Cu and Si doping can greatly facilitate photogenerated charge separation and migration for photocatalytic methane conversion. Moreover, electrochemical impedance measurements further evaluate the charge transport. All TiO_2 nanosheets exhibit a positive slope in the Mott-Schottky plot (Fig. S10, ESI[†]). Specifically, the slopes for doped TiO_2 nanosheets are more obviously gradual than that of the pristine TiO_2 nanosheets, which qualitatively indicates a higher charge carrier density according to the Mott-Schottky equation.³⁹ Overall, the improved photocatalytic performance

for doped TiO_2 could be mainly attributed to the enhanced charge separation and migration.

To gain insight into the electron transfer of TiO_2 nanosheets upon Cu and Si doping, we monitored the oxidation state changes of doped Cu and Si in TiO_2 nanosheets during the photocatalytic reaction using irradiated XPS. Specifically, the Cu 2p XPS spectrum shifts towards a lower binding energy upon light irradiation (Fig. 4b), while no obvious shift can be observed in the Si 2p XPS spectrum (Fig. S11, ESI[†]). In addition, light-irradiated EPR measurements were carried out to further elucidate the change in the oxidation state of Cu under light irradiation. The differences between the EPR spectra under light irradiation (Fig. S12, ESI[†]) and the spectrum in the dark (Fig. S6, ESI[†]) are shown in Fig. 4c. The positive and increasing values of the EPR difference reveal that Cu^{2+} is reduced to EPR-silent Cu^+ by photogenerated electrons under light irradiation. Interestingly, the EPR spectrum for the irradiated $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ would recover to its initial state after exposure to air for 20 min (Fig. S13, ESI[†]), suggesting the high photocatalytic stability of the co-doped TiO_2 nanosheets. Taken together, these results illustrate that doping could significantly enhance the separation of photogenerated carriers and the activation of methane molecules on the surface.

We then performed *in situ* diffuse reflectance infrared Fourier transform spectroscopy (DRIFTS) to observe the intermediates in the photocatalytic methane conversion process to analyse the reaction mechanism. The *in situ* DRIFTS in the presence of CH_4 and water vapour for $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ (Fig. 4d) exhibit obvious peaks at 1304 and 1540 cm^{-1} , assigned to the C-H deformation vibration and symmetric deformation vibration of CH_4 , respectively.^{40,41} It is worth mentioning that the C-H symmetric vibration of CH_4 at 1540 cm^{-1} is normally infrared-forbidden for free methane molecules, which manifests the efficient adsorption of CH_4 molecules on the $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ surface.⁴² The C-H symmetric stretching vibration of CH_4 intensified immediately upon illumination, indicating photoenhanced methane adsorption. Moreover, the vibration modes of CH_2/CH_3 deformation at new peaks at $1470/1425 \text{ cm}^{-1}$, and the C-O stretching vibrational mode at 1042 cm^{-1} appear and grow gradually in the DRIFTS of $\text{TiO}_2(\text{Si})-1\% \text{Cu}$, demonstrating the dissociation of CH_4 molecules over the $\text{TiO}_2(\text{Si})-1\% \text{Cu}$ catalyst surface under light irradiation.⁴³ In sharp contrast, the CH_2/CH_3 and C-O species are hardly resolved in the DRIFTS for pristine TiO_2 nanosheets (Fig. S14, ESI[†]). These results firmly reveal that the Cu and Si co-doping can rationally modulate adsorption configuration of reactant molecules on the surface and significantly boost the cleavage of methane on the TiO_2 nanosheets.

3. Conclusions

In conclusion, we have provided an efficient candidate for photocatalytic methane conversion into ethane through Cu and Si co-doping into ultrathin TiO_2 nanosheets. It is demonstrated that the co-doping strategy can rationally alter the

reactive oxygen species for efficient activation of the C–H bond according to the *in situ* EPR. Furthermore, Cu and Si doping greatly improves the efficiency of photogenerated charge separation and migration. As a result, the optimized TiO₂(Si)–1%Cu achieves a C₂H₆ production rate of 33.8 μmol g^{−1} h^{−1} with a selectivity of 88.4% upon 4 h light irradiation. This work presents a fresh perspective on the photocatalytic activation of C–H bonds under mild conditions and paves the way for efficient methane conversion into value-added chemicals through a highly sustainable approach.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge financial support from the National Key R&D Program of China (2020YFA0406103), NSFC (22232003, 21725102, 22122506, 22279128, 91961106, 22075267, 21950410514, 22109148), Strategic Priority Research Program of the CAS (XDPEB14), Anhui Provincial Natural Science Foundation (2008085J05), Youth Innovation Promotion Association of CAS (2019444), China Postdoctoral Science Foundation (2021M703122), Jiangsu Funding Program for Excellent Postdoctoral Talent, Gusu Innovation and Entrepreneurship Leading Talents Program (ZXL2022386) and Users with Excellence Program of Hefei Science Center CAS (2020HSC-UE003). *In situ* DRIFTS measurements were performed at the Infrared Spectroscopy and Microspectroscopy Endstation (BL01B) of NSRL. We thank the support from USTC Center for Micro- and Nanoscale Research and Fabrication.

References

- H. Song, X. Meng, Z.-J. Wang, H. Liu and J. Ye, *Joule*, 2019, **3**, 1606–1636.
- J. Low, J. Ma, J. Wan, W. Jiang and Y. Xiong, *Acc. Mater. Res.*, 2022, **3**, 331–342.
- J. Ma, R. Long, D. Liu, J. Low and Y. Xiong, *Small Struct.*, 2022, **3**, 2100147.
- X. Meng, X. Cui, N. P. Rajan, L. Yu, D. Deng and X. Bao, *Chem*, 2019, **5**, 2296–2325.
- P. Schwach, X. Pan and X. Bao, *Chem. Rev.*, 2017, **117**, 8497–8520.
- X. Shen, D. Wu, X.-Z. Fu and J.-L. Luo, *Chin. Chem. Lett.*, 2022, **33**, 390–393.
- V. L. Sushkevich, D. Palagin, M. Ranocchiari and J. A. van Bokhoven, *Science*, 2017, **356**, 523–527.
- B. E. R. Snyder, P. Vanelderen, M. L. Bols, S. D. Hallaert, L. H. Böttger, L. Ungur, K. Pierloot, R. A. Schoonheydt, B. F. Sels and E. I. Solomon, *Nature*, 2016, **536**, 317–321.
- W.-J. Jang, J.-O. Shim, H.-M. Kim, S.-Y. Yoo and H.-S. Roh, *Catal. Today*, 2019, **324**, 15–26.
- J. Ma, K. Mao, J. Low, Z. Wang, D. Xi, W. Zhang, H. Ju, Z. Qi, R. Long, X. Wu, L. Song and Y. Xiong, *Angew. Chem., Int. Ed.*, 2021, **60**, 9357–9361.
- S. Song, H. Song, L. Li, S. Wang, W. Chu, K. Peng, X. Meng, Q. Wang, B. Deng, Q. Liu, Z. Wang, Y. Weng, H. Hu, H. Lin, T. Kako and J. Ye, *Nat. Catal.*, 2021, **4**, 1032–1042.
- Y. Li, L. Wang, J. Low, D. Wu, C. Hu, W. Jiang, J. Ma, C. Wang, R. Long, L. Song, H. Xu and Y. Xiong, *Chin. Chem. Lett.*, 2020, **31**, 231–234.
- Y. Kato, H. Yoshida and T. Hattori, *Chem. Commun.*, 1998, 2389–2390.
- H. Yoshida, N. Matsushita, Y. Kato and T. Hattori, *J. Phys. Chem. B*, 2003, **107**, 8355–8362.
- L. Li, Y.-Y. Cai, G.-D. Li, X.-Y. Mu, K.-X. Wang and J.-S. Chen, *Angew. Chem., Int. Ed.*, 2012, **51**, 4702–4706.
- Z. Chen, S. Wu, J. Ma, S. Mine, T. Toyao, M. Matsuoka, L. Wang and J. Zhang, *Angew. Chem., Int. Ed.*, 2021, **60**, 11901–11909.
- J. Xie, R. Jin, A. Li, Y. Bi, Q. Ruan, Y. Deng, Y. Zhang, S. Yao, G. Sankar, D. Ma and J. Tang, *Nat. Catal.*, 2018, **1**, 889–896.
- X. Yu, V. L. Zholobenko, S. Moldovan, D. Hu, D. Wu, V. V. Ordonsky and A. Y. Khodakov, *Nat. Energy*, 2020, **5**, 511–519.
- X. Li, J. Xie, H. Rao, C. Wang and J. Tang, *Angew. Chem., Int. Ed.*, 2020, **59**, 19702–19707.
- H. Yoshida, N. Matsushita, Y. Kato and T. Hattori, *J. Phys. Chem. B*, 2003, **107**, 8355–8362.
- M. O. Ross, F. MacMillan, J. Wang, A. Nisthal, T. J. Lawton, B. D. Olafson, S. L. Mayo, A. C. Rosenzweig and B. M. Hoffman, *Science*, 2019, **364**, 566–570.
- H. Yoshida, C. Murata and T. Hattori, *Chem. Commun.*, 1999, 1551–1552, DOI: [10.1039/A904886C](https://doi.org/10.1039/A904886C).
- Y. Zhao, Y. Zhao, R. Shi, B. Wang, G. I. N. Waterhouse, L.-Z. Wu, C.-H. Tung and T. Zhang, *Adv. Mater.*, 2019, **31**, 1806482.
- Z. Zheng, B. Huang, X. Qin, X. Zhang, Y. Dai, M. Jiang, P. Wang and M.-H. Whangbo, *Chem. – Eur. J.*, 2009, **15**, 12576–12579.
- B. Choudhury, M. Dey and A. Choudhury, *Int. Nano Lett.*, 2013, **3**, 25.
- G. Colón, M. Maicu, M. C. Hidalgo and J. A. Navío, *Appl. Catal., B*, 2006, **67**, 41–51.
- J. Ma, C. Gao, J. Low, D. Liu, X. Lian, H. Zhang, H. Jin, X. Zheng, C. Wang, R. Long, H. Ji, J. Zhu and Y. Xiong, *J. Phys. Chem. C*, 2021, **125**, 5542–5548.
- Y. Su, S. Chen, X. Quan, H. Zhao and Y. Zhang, *Appl. Surf. Sci.*, 2008, **255**, 2167–2172.
- C. Chen, Y. Wei, G. Yuan, Q. Liu, R. Lu, X. Huang, Y. Cao and P. Zhu, *Adv. Funct. Mater.*, 2017, **27**, 1701575.
- G. Li, N. M. Dimitrijevic, L. Chen, T. Rajh and K. A. Gray, *J. Phys. Chem. C*, 2008, **112**, 19040–19044.
- S. Neubert, D. Mitoraj, S. A. Shevlin, P. Pulisova, M. Heimann, Y. Du, G. K. L. Goh, M. Pacia, K. Kruczała, S. Turner, W. Macyk, Z. X. Guo, R. K. Hocking and R. Beranek, *J. Mater. Chem. A*, 2016, **4**, 3127–3138.
- F. Tian, Y. Zhang, J. Zhang and C. Pan, *J. Phys. Chem. C*, 2012, **116**, 7515–7519.
- N. Ulagappan and H. Frei, *J. Phys. Chem. A*, 2000, **104**, 7834–7839.
- S. Duhalde, M. F. Vignolo, F. Golmar, C. Chilotte, C. E. R. Torres, L. A. Errico, A. F. Cabrera, M. Rentería, F. H. Sánchez and M. Weissmann, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2005, **72**, 161313.

- 35 P. Kuppusamy and J. L. Zweier, *J. Biol. Chem.*, 1989, **264**, 9880–9884.
- 36 A. F. Carley, H. A. Edwards, B. Mile, M. W. Roberts, C. C. Rowlands, F. E. Hancock and S. D. Jackson, *J. Chem. Soc., Faraday Trans.*, 1994, **90**, 3341–3346.
- 37 P. G. Lustemberg, R. M. Palomino, R. A. Gutiérrez, D. C. Grinter, M. Vorokhta, Z. Liu, P. J. Ramírez, V. Matolín, M. V. Ganduglia-Pirovano, S. D. Senanayake and J. A. Rodríguez, *J. Am. Chem. Soc.*, 2018, **140**, 7681–7687.
- 38 H. Song, X. Meng, S. Wang, W. Zhou, X. Wang, T. Kako and J. Ye, *J. Am. Chem. Soc.*, 2019, **141**, 20507–20515.
- 39 G. Yuan, K. Aruda, S. Zhou, A. Levine, J. Xie and D. Wang, *Angew. Chem., Int. Ed.*, 2011, **50**, 2334–2338.
- 40 X. Yu, V. De Waele, A. Löfberg, V. Ordonsky and A. Y. Khodakov, *Nat. Commun.*, 2019, **10**, 700.
- 41 W. Jiang, J. Low, K. Mao, D. Duan, S. Chen, W. Liu, C.-W. Pao, J. Ma, S. Sang, C. Shu, X. Zhan, Z. Qi, H. Zhang, Z. Liu, X. Wu, R. Long, L. Song and Y. Xiong, *J. Am. Chem. Soc.*, 2021, **143**, 269–278.
- 42 D. Scarano, S. Bertarione, G. Spoto, A. Zecchina and C. Otero Areán, *Thin Solid Films*, 2001, **400**, 50–55.
- 43 R. Zhang, H. Wang, S. Tang, C. Liu, F. Dong, H. Yue and B. Liang, *ACS Catal.*, 2018, **8**, 9280–9286.