

Cite this: *Chem. Sci.*, 2019, 10, 9692

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 4th June 2019

Accepted 28th August 2019

DOI: 10.1039/c9sc02711d

rsc.li/chemical-science

# Influence of the distal guanidine group on the rate and selectivity of O<sub>2</sub> reduction by iron porphyrin†

Arnab Ghatak, Snehadri Bhakta, Sarmistha Bhunia and Abhishek Dey \*

The O<sub>2</sub> reduction reaction (ORR) catalysed by iron porphyrins with covalently attached pendant guanidine groups is reported. The results show a clear enhancement in the rate and selectivity for the 4e<sup>−</sup>/4H<sup>+</sup> ORR. *In situ* resonance Raman investigations show that the rate determining step (rds) is O<sub>2</sub> binding to ferrous porphyrins in contrast to the case of mononuclear iron porphyrins and heme/Cu analogues where the O–O bond cleavage of a heme peroxide is the rds. The selectivity is further enhanced when an axial imidazole ligand is introduced. Thus, the combination of the axial imidazole ligand and pendant guanidine ligand, analogous to the active site of peroxidases, is determined to be very effective in enabling a facile and selective 4e<sup>−</sup>/4H<sup>+</sup> ORR.

## Introduction

The factors that affect the rate and selectivity of the catalytic oxygen reduction reaction (ORR) are of fundamental interest as it is an essential process for several energy conversion technologies ranging from fuel cells to metal air batteries.<sup>1</sup> The ORR can proceed either *via* a 2e<sup>−</sup>/2H<sup>+</sup> pathway to produce H<sub>2</sub>O<sub>2</sub> or *via* a 4e<sup>−</sup>/4H<sup>+</sup> pathway to produce water.<sup>2</sup> The latter pathway is favoured both from a thermodynamic point of view<sup>2</sup> and because it avoids partially reduced oxygen species (PROS) such as H<sub>2</sub>O<sub>2</sub> and O<sub>2</sub><sup>−</sup> which are very reactive and often detrimental to the catalyst.<sup>3</sup> Iron porphyrins have been long used to extensively investigate the O<sub>2</sub> reduction process in solution as well as under heterogeneous electrochemical conditions by immobilizing them on electrodes (Fig. 1A).<sup>4–6</sup> Erstwhile investigations have revealed that these complexes prefer 2e<sup>−</sup>/2H<sup>+</sup> reduction of O<sub>2</sub> resulting in H<sub>2</sub>O<sub>2</sub>.<sup>7</sup>

Inspiration for ORR catalyst design can be obtained from nature as the ORR is a key process in cell metabolism. Eukaryotes use molecular oxygen as the terminal electron acceptor in the final stage of the respiration process where cytochrome c oxidase (CcO) catalyses the reduction of O<sub>2</sub> to H<sub>2</sub>O to drive the oxidative phosphorylation activity.<sup>8</sup> CcO belongs to the heme–Cu oxidase superfamily of enzymes and its active site comprises a bimetallic heme/Cu core and a post transitionally modified Tyr244 residue (Fig. 1B).<sup>9,10</sup> The mechanism of the CcO assisted ORR was extensively investigated using its elaborate structural and functional mimics, to design a suitable molecular electrocatalyst. Unlike mononuclear iron porphyrins, these

analogues produce minimal PROS and catalyse the electrochemical 4e<sup>−</sup>/4H<sup>+</sup> ORR at neutral pH under heterogeneous conditions with 2<sup>nd</sup> order rates of 10<sup>5</sup> M<sup>−1</sup> s<sup>−1</sup>.<sup>4,11–13</sup> The

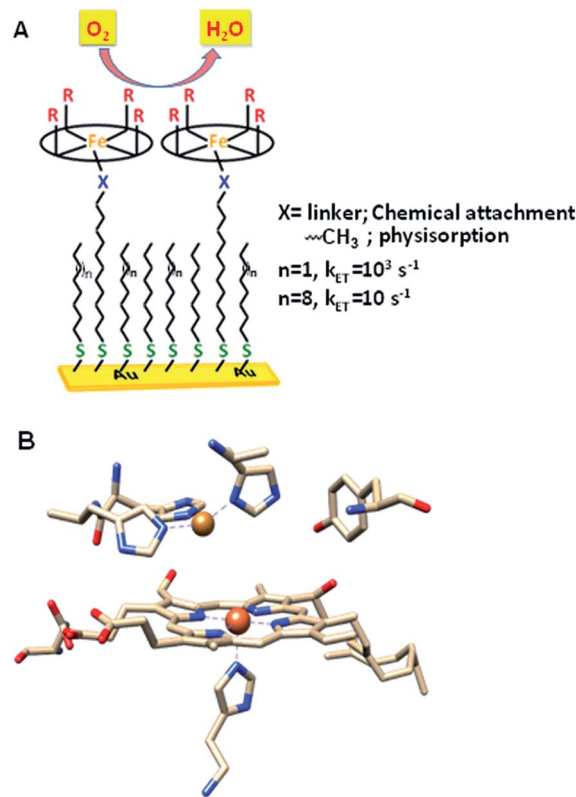


Fig. 1 (A) Heterogeneous electrochemical construct (the oval ring represents the porphyrin ligand); (B) binuclear active site of CcO (PDB ID: 1OCC).<sup>9</sup>

School of Chemical Sciences, Indian Association for the Cultivation of Science, 2A & 2B Raja S. C. Mullick Road, Jadavpur, Kolkata, 700032, India. E-mail: icad@iacs.res.in

† Electronic supplementary information (ESI) available: Experimental details, the synthetic procedure, construction of electrodes, spectral data, electrochemical data and DFT optimized structures. See DOI: 10.1039/c9sc02711d

generation of PROS was thought to occur *via* hydrolysis of dioxygen derived intermediates ( $\text{Fe}^{\text{III}}\text{-O}_2^-$  and/or  $\text{Fe}^{\text{III}}\text{-OOH}$ )<sup>14</sup> and the extent of PROS generation increases with a decrease in electron flux from the electrode to the catalyst.<sup>15</sup> The electron flux can be conveniently tuned between 1 and 100 000  $\text{s}^{-1}$  by utilizing self-assembled monolayer covered Au electrodes where the electron tunnelling rate depends on the chain length of the thiol used.<sup>16,17</sup> Recent reports show that similar selectivity and rates can be obtained by using iron porphyrins bearing both hydrogen bonding and redox active moieties such as ferrocene even under slow electron flux from the electrode.<sup>18,19</sup>

Recently surface enhanced resonance Raman spectroscopy coupled to rotating disk electrochemistry (SERRS-RDE) has been utilised for detection of intermediates accumulated when the electrocatalyst is in a steady state.<sup>20</sup> The results reveal that one of the key intermediates produced during the ORR cycle catalysed by iron porphyrins is a low spin  $\text{Fe}^{\text{III}}\text{-OOH}$  species.<sup>21</sup> The O–O bond of this species is strong and the step leading to its cleavage is the rate determining step (rds) of the electrochemical ORR for several iron porphyrins and heme/Cu systems.<sup>13,20,22</sup> The facile cleavage of the O–O bond requires protonation of the distal oxygen of the  $\text{Fe}^{\text{III}}\text{-OOH}$  species for the anionic thiolate and phenolate axial ligands or reduction to a  $\text{Fe}^{\text{II}}\text{-OOH}$  species for neutral axial ligands to form water.<sup>14,15,23</sup> The protonation of the distal oxygen (one bound to proton) of a  $\text{Fe}^{\text{III}}\text{-OOH}$  species leads to heterolytic O–O bond cleavage and subsequent release of water (Scheme 1, pathway 1). However, the protonation of the proximal oxygen (one bound to the iron) leading to hydrolysis and release of  $\text{H}_2\text{O}_2$  is favoured due to a 1.5 unit higher  $\text{pK}_a$  of the proximal oxygen relative to the distal oxygen (Scheme 1, pathway 3).<sup>20,24–26</sup> In iron porphyrins with neutral axial ligands the O–O bond cleavage in the subsequent steps requires electron transfer (ET).<sup>18,27</sup> Thus, when ET is inhibited, the extent of  $\text{H}_2\text{O}_2$  release is increased. However, if the O–O bond can be activated for protonation and stabilized by hydrogen bonding one may be able to enhance the rate and selectivity of the ORR. Accordingly, distal amine groups and heteroatoms that can specifically deliver protons to the distal oxygen have been shown to facilitate the selective protonation of the distal oxygen atom of this  $\text{Fe}^{\text{III}}\text{-OOH}$  intermediate resulting in very facile and selective  $4\text{e}^-/4\text{H}^+$  reduction of  $\text{O}_2$  by mononuclear iron porphyrins.<sup>2,26</sup>

In our continued pursuit of understanding the role of the distal superstructure of the porphyrin active site we are drawn to peroxidases. Heme peroxidases are ubiquitous in nature,

where they catalyse the oxidation of organic substrates using  $\text{H}_2\text{O}_2$ .<sup>28</sup> The presence of basic distal residues such as Arg38 and His42 in the distal site (Fig. 2A)<sup>29</sup> facilitates the O–O bond cleavage of a LS  $\text{Fe}^{\text{III}}\text{-OOH}$  species to form compound I *via* selective protonation of the distal oxygen atom – the pull effect.<sup>30</sup> Recently, a mononuclear iron porphyrin *o*-monoguanidinotetraphenyliron(III)-porphyrin ( $\text{Fe}^{\text{III}}\text{Cl-MARG}$ , Fig. 2B,  $\text{R} = \text{H}$ ) mimicking the active site of HRP has been developed where a covalently attached guanidium moiety is included in the second sphere mimicking the Arg38 group of HRP. This iron porphyrin is a functional model of HRP and can catalyse the oxidation of most HRP substrates with  $\text{H}_2\text{O}_2$ . This biomimetic functional model utilizes the ‘ping pong’ mechanism for substrate oxidation akin to HRP with  $K_{\text{M}}$  and  $k_{\text{cat}}$  values similar to those of the native enzyme.<sup>31</sup>

In this manuscript, the electrochemical oxygen reduction activity of a series of guanidine bearing iron porphyrins is investigated under heterogeneous electrochemical conditions in aqueous solvents, along with their initial spectroscopic and theoretical characterisation. These porphyrins vary in their substitution of the guanidine moiety (Fig. 2B). The results indicate that the inclusion of the guanidine group in the distal environment of a synthetic iron porphyrin enhances the selectivity as well as the rate of the  $4\text{e}^-/4\text{H}^+$  ORR. The rates and selectivity are substantially affected either by inclusion of an axial imidazole ligand or by making the distal pocket more hydrophobic.


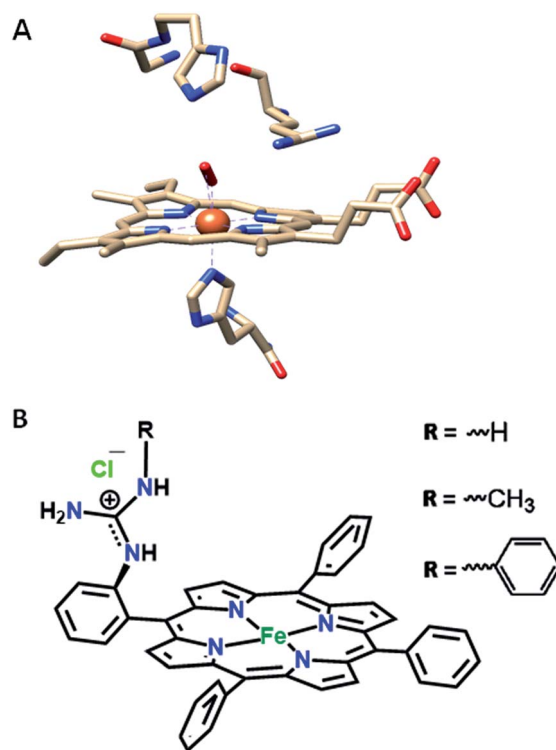


Fig. 2 (A) The active site structure of HRP (PDB ID: 1H57);<sup>32</sup> (B) pictorial representation of all the electrocatalysts used ( $\text{R} = \text{H}$ ,  $\text{Fe}^{\text{III}}\text{Cl-MARG}$ ;  $\text{R} = \text{methyl}$ ,  $\text{Fe}^{\text{III}}\text{Cl-MeMARG}$  and  $\text{R} = \text{phenyl}$ ,  $\text{Fe}^{\text{III}}\text{Cl-PhMARG}$ ).



Scheme 1 Schematic representation of factors determining the  $2\text{e}^-/2\text{H}^+$  vs.  $4\text{e}^-/4\text{H}^+$  ORR selectivity of porphyrin complexes. (The oval ring represents the porphyrin ligand.)<sup>26</sup>

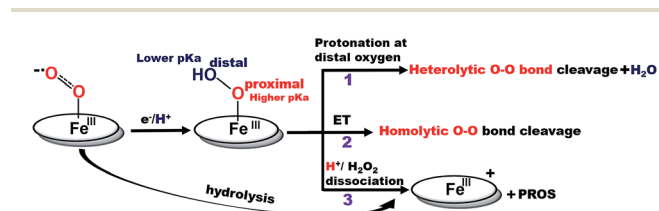

## Results

The iron porphyrin complexes (Fig. 2) are physisorbed over edge plane graphite (EPG) electrodes and alkyl thiol SAM ( $C_8SH/C_{16}SH$ ) covered Au electrodes, and electrochemical data are collected in pH 7 phosphate buffer solution against a Ag/AgCl in saturated KCl reference electrode and a Pt counter electrode. The electron transfer rates vary between  $10^5$  and  $10^1$  s $^{-1}$  between EPG and  $C_{16}SH$  SAM and this allows evaluation of the role of the pendant guanidine group in stabilizing the intermediates formed during the ORR (Scheme 1) against hydrolysis. The further activation of these species for O–O bond cleavage requires reduction and in the absence of rapid electron flux from the electrode it enhances the release of PROS *via* hydrolysis. These iron porphyrins can also be chemically attached to the electrode using a mixed thiol SAM combining linker Imd $C_{11}SH$  and diluent  $C_8SH$  (Imd $C_{11}SH$  SAM) functionalised Au electrode where the imidazole terminal of the SAM acts as an axial ligand (Fig. 1A, ESI†). SERRS data show that the iron porphyrins are in their high spin state bearing an axial –OH ligand with the Fe–OH frequency at 585 cm $^{-1}$  (Fig. S3, ESI†). The cyclic voltammetry (CV) data of Fe<sup>III</sup>Cl–MARG show a well-developed Fe<sup>III/II</sup> redox couple for the complex in all the constructs in the absence of O $_2$  at pH 7. For the EPG electrode and  $C_8SH$  SAM covered Au electrodes, the  $E_{1/2}$  value of the Fe<sup>III/II</sup> process of Fe–MARG is at –255 mV (Fig. 3A green) and –253 mV

(Fig. 3A red), respectively, *vs.* Ag/AgCl, while that for imidazole bound Fe–MARG is at –221 mV (Fig. 3A blue) *vs.* Ag/AgCl. Integrating these redox waves, the surface coverage is found to be  $0.73 \pm 0.60 \times 10^{-12}$ ,  $1.86 \pm 0.40 \times 10^{-12}$ , and  $4.84 \pm 0.30 \times 10^{-12}$  mol cm $^{-2}$  over the EPG electrode,  $C_8SH$  SAM- and Imd $C_{11}SH$  SAM modified Au electrodes, respectively. In air saturated pH-7 buffer the reversible couple disappears and is replaced by a large irreversible oxygen reduction current indicating the electrocatalytic ORR by Fe<sup>III</sup>Cl–MARG (Fig. 3B). The LSV data show that at the EPG electrode Fe(III)–Cl–MARG reduces O $_2$  at a potential of –240 mV (Fig. 3B green). In contrast, on  $C_8SH$  SAM and Imd $C_{11}SH$  SAM the complex shows the ORR at a further negative potential of –313 mV (Fig. 3B red) and –368 mV (Fig. 3B blue), respectively, *vs.* Ag/AgCl compared to the Fe<sup>III/II</sup> reduction potential indicating that the reduction from Fe<sup>III</sup> to Fe<sup>II</sup> is not the potential determining step or thermodynamically the most uphill process of the ORR when these complexes are immobilized on SAM.

Rotating disk electrochemistry (RDE) data of Fe<sup>III</sup>Cl–MARG on EPG indicate a normal substrate diffusion limited current for the complex below –240 mV (Fig. 3C). The K–L plot of  $1/I_{cat}$  *vs.*  $1/\omega^{1/2}$  is linear and the slope is close to the theoretical value for the 4e $^{-}$  reduction process of O $_2$ . The 2<sup>nd</sup> order rate constant for the electrocatalytic ORR by this complex is calculated using K–L analysis. The  $k_{cat}$  value obtained in the EPG electrode is  $4.2 \times 10^6$  M $^{-1}$  s $^{-1}$ , which exceeds those of synthetic heme/Cu CcO model systems by one order of magnitude.<sup>33</sup> Thus, the iron porphyrin having a guanidium moiety in the 2<sup>nd</sup> sphere, emulating the ‘pull effect’ of HRP, increases the rate and selectivity of the 4e $^{-}/4H^{+}$  ORR substantially compared to unfunctionalized porphyrins.

In the rotating ring disk electrochemistry (RRDE) experiment, partially reduced oxygen species (PROS) such as H $_2$ O $_2$ /O $_2^{-}$  produced on the working electrode diffuses to the Pt ring electrode encircling the disk electrode where it can be oxidised back to O $_2$  allowing quantitative detection of PROS (Fig. 4). The Fe<sup>III</sup>Cl–MARG physisorbed over the EPG electrode,  $C_8SH$  SAM covered, and  $C_{16}SH$  SAM covered Au electrodes produce  $2.54 \pm 0.1\%$ ,  $8.85 \pm 0.1\%$  and  $18 \pm 0.2\%$  PROS (Table 1), respectively. The rate of electron transfer (ET) from the electrode to the catalyst is  $>10^5$  s $^{-1}$ ,  $10^3$  s $^{-1}$ , and  $10$  s $^{-1}$  for EPG,  $C_8SH$  and  $C_{16}SH$  SAM, respectively.<sup>34</sup> Thus, with a decrease in the electron transfer rate from the electrode, *i.e.* with the increase in the chain length of the SAM, the rate of hydrolysis of the hydroperoxide intermediate species (Scheme 1) and PROS formation increases. Fe<sup>III</sup>Cl–MARG produces a maximum of 18% PROS in contrast to iron porphyrins with hydrogen bonding triazole residues in the distal pocket which produce  $\sim 100\%$  PROS.<sup>19</sup> Although the distal guanidine can enhance the selectivity towards 4e $^{-}/4H^{+}$  reduction of oxygen, it is not as efficient as the recently reported mono-nuclear porphyrins with pendant primary amines or pyridine.<sup>26</sup>

Two structural variants of Fe<sup>III</sup>Cl–MARG are evaluated as well, namely *o*-monomethylguanidinetetraphenyliron(III)–porphyrin (Fe<sup>III</sup>Cl–MeMARG) and *o*-monophenylguanidinetetraphenyliron(III)–porphyrin (Fe<sup>III</sup>Cl–PhMARG) (Fig. 2). The  $^1H$  NMR data of the free ligand of

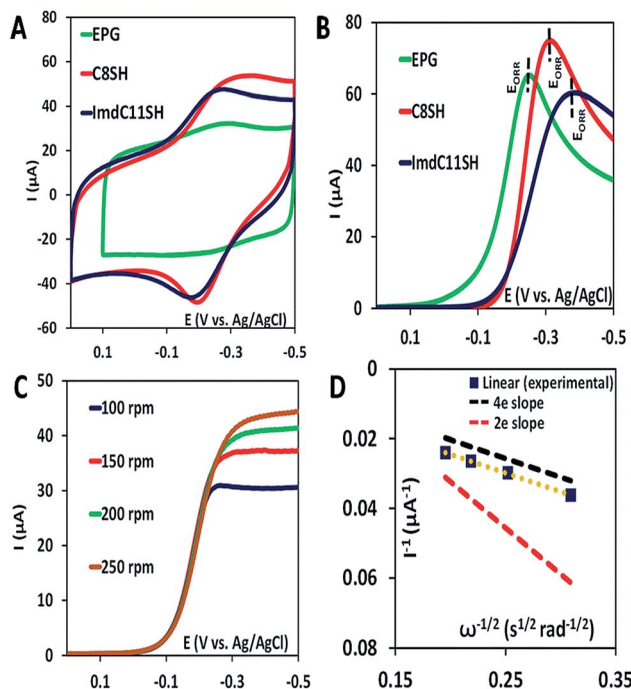


Fig. 3 (A) CV data of Fe<sup>III</sup>Cl–MARG over the EPG electrode (green),  $C_8SH$  SAM- (red) and Imd $C_{11}SH$  SAM (blue) modified Au electrodes in the absence of O $_2$  in pH 7 phosphate buffer with KPF $_6$  supporting electrolyte at a scan rate of 1 V s $^{-1}$ ; (B) LSV data of the complex in air saturated pH 7 phosphate buffer over EPG (green),  $C_8SH$  SAM (red) and Imd $C_{11}SH$  SAM (blue) at 0 rpm at a scan rate of 50 mV s $^{-1}$ ; (C) RDE plots of the catalyst over the EPG electrode for multiple rotations at a scan rate of 50 mV s $^{-1}$ ; (D) K–L plot of the catalyst at a potential of –0.5 V.



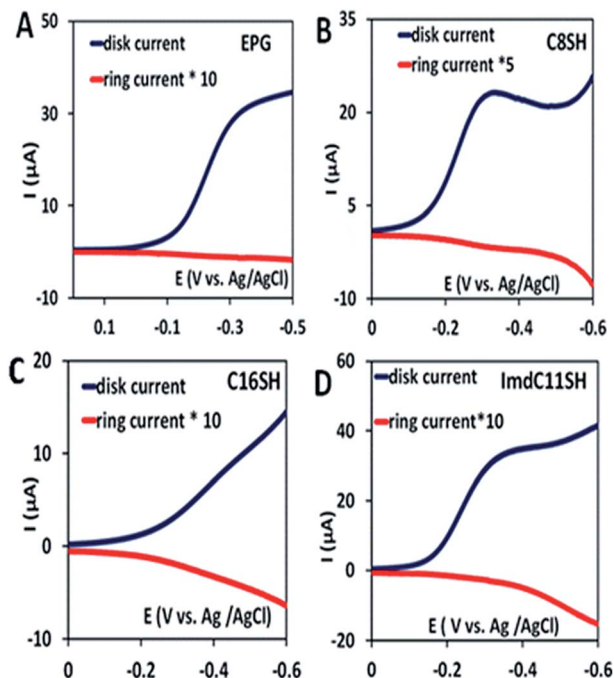


Fig. 4 RRDE data of the complex on the EPG electrode (A), C<sub>8</sub>SH SAM modified Au electrode (B), C<sub>16</sub>SH SAM modified Au electrode (C), and ImdC<sub>11</sub>SH SAM modified Au electrode (D) at a scan rate of 10 mV s<sup>-1</sup> at 300 rpm using a Pt counter electrode and Ag/AgCl (sat. KCl) as a reference electrode.

MeMARG and PhMARG (details in the ESI<sup>†</sup>) in CDCl<sub>3</sub> show that the resonances for the methyl CHs of the guanidine group (Fig. 2, R = methyl) are at 1.35 ppm (Fig. 5A) and the resonances for the aromatic CHs of the guanidine Ph group (Fig. 2, R = phenyl) are at 5.8, 6.2, and 6.4 ppm (Fig. 5B). The <sup>1</sup>H resonances of the guanidine substituents indicate that both methyl and phenyl protons are shielded by the aromatic porphyrin group implying that these groups are poised on top of the porphyrin ring. This ought to make the environment of the distal site of the iron porphyrin more hydrophobic. The iron complexes of these ligands show a clear Fe<sup>III/II</sup> redox process under a N<sub>2</sub> atmosphere in pH 7 phosphate buffer (Fig. S7 and S8, ESI<sup>†</sup>). In the presence of air saturated pH 7 phosphate buffer both Fe<sup>III</sup>Cl–MeMARG and Fe<sup>III</sup>Cl–PhMARG show catalytic ORR currents. Using RRDE the amounts of PROS produced for Fe<sup>III</sup>Cl–MeMARG are determined to be 2.40 ± 0.3%, 5.43 ± 0.5%, 7.9 ± 0.1% for the

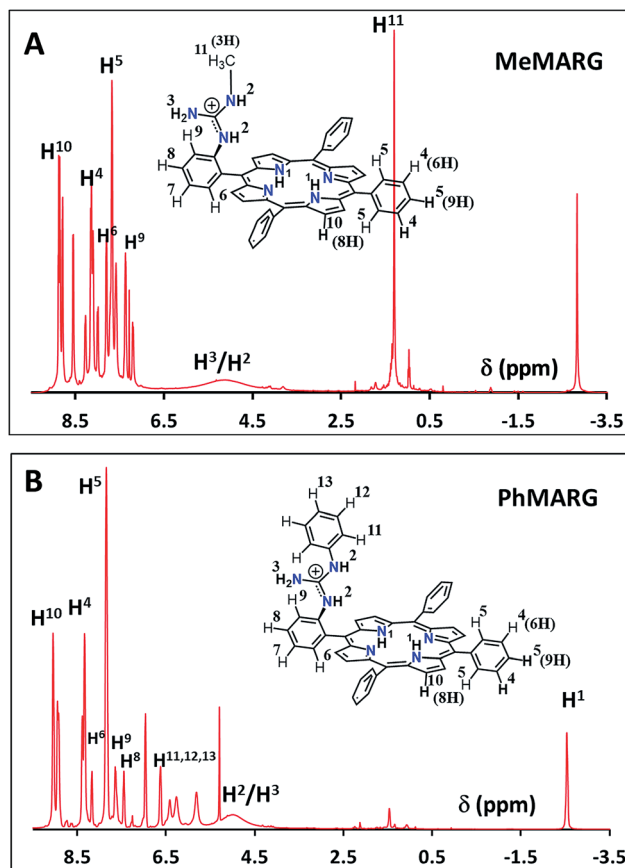


Fig. 5 <sup>1</sup>H NMR spectra of (A) MeMARG and (B) PhMARG in CDCl<sub>3</sub>.

ORR when it is physisorbed over EPG, C<sub>8</sub>SH and C<sub>16</sub>SH SAM, respectively (Fig. S9, ESI<sup>†</sup>). In the case of Fe<sup>III</sup>Cl–PhMARG the same trend is followed with a maximum of 9.20 ± 0.4% PROS on C<sub>16</sub>SH SAM and only 1.80 ± 0.1% PROS on EPG (Fig. S10, ESI<sup>†</sup>, Table 1). These data clearly indicate that the % PROS released during the ORR decreases as more hydrophobic residues are included in the pendant guanidine group, enhancing the selectivity towards the 4e<sup>-</sup>/4H<sup>+</sup> ORR. The presence of methyl and phenyl groups just on top of the porphyrin ring likely creates a hydrophobic environment, which slows the hydrolysis of the hydroperoxide intermediate species (Scheme 1).

In nature, the heme in the active site of HRP is bound to the protein *via* an axial histidine ligand (Fig. 1B) which has an

Table 1 Electrochemical ORR data

| Catalyst                    | PROS analysis (%)                                   |                                                                   |                                                       |                                                                       |
|-----------------------------|-----------------------------------------------------|-------------------------------------------------------------------|-------------------------------------------------------|-----------------------------------------------------------------------|
|                             | EPG <sup>a</sup> (10 <sup>6</sup> s <sup>-1</sup> ) | C <sub>8</sub> SH <sup>a</sup> (10 <sup>3</sup> s <sup>-1</sup> ) | C <sub>16</sub> SH <sup>a</sup> (10 s <sup>-1</sup> ) | ImdC <sub>11</sub> SH <sup>a</sup> (10 <sup>3</sup> s <sup>-1</sup> ) |
| Fe <sup>III</sup> Cl–MARG   | 2.54 ± 0.1                                          | 8.85 ± 0.1                                                        | 18.0 ± 0.2                                            | 4.95 ± 0.4                                                            |
| Fe–MARG–N–MeImd             | 1.43 ± 0.2                                          | 3.10 ± 0.5                                                        | 7.00 ± 0.1                                            | NA                                                                    |
| Fe <sup>III</sup> Cl–MeMARG | 2.40 ± 0.3                                          | 5.43 ± 0.5                                                        | 7.9 ± 0.1                                             | 2.64 ± 0.1                                                            |
| Fe <sup>III</sup> Cl–PhMARG | 1.80 ± 0.1                                          | 4.73 ± 0.5                                                        | 9.20 ± 0.4                                            | 1.32 ± 0.1                                                            |

<sup>a</sup> Standard rate of electron transfer.

imidazole head group. The axial imidazole ligand can be introduced in  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  either *via* using an imidazole group terminated SAM or by chemically binding an imidazole to  $\text{Fe-MARG}$  before its immobilization on the electrode. First, when  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  is chemically attached to  $\text{ImdC}_{11}\text{SH SAM}$ , the RRDE experiments show that it produces only  $4.95 \pm 0.4\%$  PROS (Fig. 4D and Table 1) during the ORR, which is almost half of the PROS produced when  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  is physisorbed atop  $\text{C}_8\text{SH}$ . Similarly,  $\text{Fe}^{\text{III}}\text{Cl-MeMARG}$  and  $\text{Fe}^{\text{III}}\text{Cl-PhMARG}$  produce  $2.64 \pm 0.3\%$  and  $1.32 \pm 0.1\%$  PROS when attached to imidazole SAM (Fig. S9 and S10, ESI†). Alternatively, an *N*-methyl imidazole bound  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  ( $\text{Fe-MARG-N-MeImd}$ ) complex is obtained by addition of 5 eq. *N*-methyl-imidazole to the solution of the complex and confirmed through the UV titration technique (details in the ESI†). In the absorption spectra,  $\text{Fe-MARG-N-MeImd}$  shows a Soret band at 413 nm and Q bands at 558 nm and 605 nm with the disappearance of characteristic Q bands (511 nm, 580 nm and 690 nm) of  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  (Fig. 6A).  $\text{Fe-MARG-N-MeImd}$  is physisorbed over the EPG electrode,  $\text{C}_8\text{SH-}$  and  $\text{C}_{16}\text{SH SAM}$ -covered Au electrodes and its heterogeneous electrochemical ORR is evaluated (Fig. S11, ESI†). The RRDE experiments show only  $1.43 \pm 0.2$ ,  $3.0 \pm 0.5\%$  and  $7.0 \pm 0.05\%$  (Fig. S12, ESI† Table 1) PROS over the EPG electrode,  $\text{C}_8\text{SH-}$  and  $\text{C}_{16}\text{SH SAM}$ -covered Au electrodes, respectively. The K-L analysis of this  $\text{Fe-MARG-N-MeImd}$  complex adsorbed on the EPG electrode (Fig. 6B) yields a 2<sup>nd</sup> order rate constant for the  $4\text{e}^-/4\text{H}^+$  ORR of  $1.76 \times 10^6 \text{ M}^{-1} \text{ s}^{-1}$ . These data clearly indicate that the combination of “push” of imidazole and “pull” of guanidine is very effective in allowing a facile and selective ORR for mononuclear iron porphyrins.

The SERRS-RDE data of  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  adsorbed on the  $\text{C}_8\text{SH SAM}$  modified Ag electrode at  $-0.5 \text{ V vs. Ag/AgCl (sat. KCl)}$  do not show any characteristic oxidation or spin state marker band corresponding to a LS  $\text{Fe}^{\text{III}}$  species as observed for simple iron porphyrins and synthetic models of  $\text{CcO}$ , rather unreacted HS  $\text{Fe}^{\text{II}}$  species is observed with  $\nu_4$  and  $\nu_2$  at  $1349 \text{ cm}^{-1}$  and  $1548 \text{ cm}^{-1}$ , respectively (Fig. 7 and S4†). The presence of the reactant HS  $\text{Fe}^{\text{II}}$  state in a catalytic steady state implies that  $\text{O}_2$  binding to the iron is the rds of catalysis commensurate with the proposal that the O-O cleavage is no longer the rds for the iron porphyrin with pendant guanidine groups.

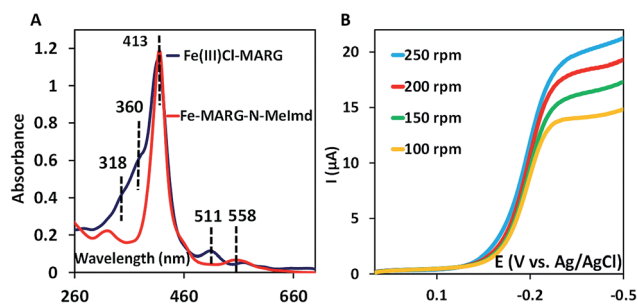


Fig. 6 (A) Absorption spectra of  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  (blue) and  $\text{Fe-MARG-N-MeImd}$  (red); (B) RDE plots of  $\text{Fe-MARG-N-MeImd}$  over EPG at a scan rate of  $50 \text{ mV s}^{-1}$  for multiple rotations.

Over the last few years we have explored several factors that affect the selective and facile  $4\text{e}^-/4\text{H}^+$  ORR using iron porphyrins. These include the “push” effect of thiolate, presence of 2<sup>nd</sup> sphere electron transfer and hydrogen bonding effects.<sup>15,26,35,36</sup> Previously the best results were obtained with synthetic mimics of  $\text{CcO}$  which includes a redox active Cu and phenol (Fig. 8B and Table 2 row 2). The direct *in situ* SERRS-RDE results for the system clearly indicated that the rate is determined by the rate of O-O bond cleavage of a LS  $\text{Fe}^{\text{III}}\text{-OOH}$  species while the selectivity is determined by the site of protonation *i.e.* on the distal/proximal oxygen atom of the LS  $\text{Fe}^{\text{III}}\text{-OOH}$  intermediate.<sup>20,21</sup> Although the push effect of a thiolate enhances the  $\text{pK}_a$  of the bound hydroperoxide making the protonation of this species efficient resulting in faster O-O bond cleavage, the protonation is not selective in the distal oxygen atom and substantial  $\text{H}_2\text{O}_2$  is released (Fig. 8A and Table 2, row 1).<sup>15</sup> In contrast, inclusion of additional electron donor groups does not help the selectivity as the peroxide intermediate is prone to hydrolysis compromising the selectivity (Fig. 8D and Table 2, row 4).<sup>37,38</sup> However, when stabilisation of this intermediate *via* H-bonding or bonding with a distal metal atom is included along with the ET site (*e.g.*  $\text{FeFc}_4$  and  $\text{FeCu-phenol}$ ) there is a distinct improvement in selectivity (Fig. 8C and Table 2, row 3; Fig. 8B and Table 2, row 2).<sup>11,35</sup> The rate, on the other hand, depends solely on the extent of activation of the O-O bond of the bound peroxide. The activation of the O-O bond can be achieved by a distal metal like Cu (Fig. 8B). The O-O bond cleavage in heme/Cu systems can be further enhanced by H-bonding to a bridging  $\text{Fe-O-O-Cu}$  peroxide.<sup>39</sup> The same is most conveniently achieved in mononuclear porphyrins by introducing protonated basic groups that can form H-bonds as well as translocate protons to the distal oxygen of the bound peroxide (Fig. 8E and Table 2, row 5).<sup>26</sup> The iron porphyrins discussed here are designed to do the same. Geometry optimized DFT calculations of the putative imidazole bound LS

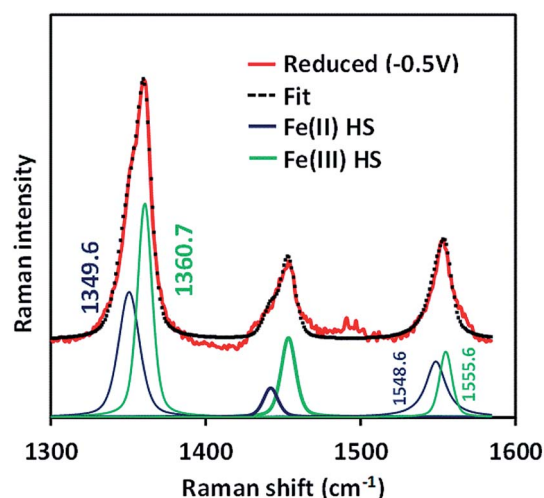


Fig. 7 SERRS-RDE data of  $\text{Fe}^{\text{III}}\text{Cl-MARG}$  physisorbed on a  $\text{C}_8\text{SH SAM}$  modified Ag disc, at reducing potential ( $-0.5 \text{ V}$ , red) in pH 7 phosphate buffer under aerobic conditions at a constant rotation rate of 200 rpm along with its Lorentzian fit showing different components.



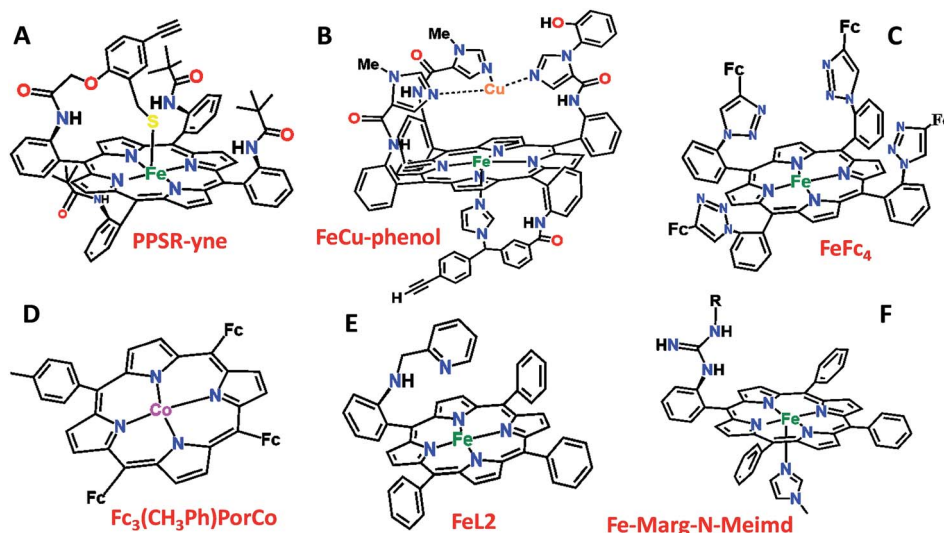


Fig. 8 Pictorial representation of all the electrocatalysts used in Table 2. Fc: ferrocene.

Table 2 Comparison of rates and % PROS values of different porphyrins

| Catalysts                       | Effect                                                                | Rate ( $K_{cat}$ ) ( $M^{-1} s^{-1}$ ) | PROS (%) $C_{16}SH$ SAM | Ref. |
|---------------------------------|-----------------------------------------------------------------------|----------------------------------------|-------------------------|------|
| PPSR-yne (Fig. 8A)              | Only 'push' from the axial site                                       | $1.11 \times 10^7$                     | 22                      | 15   |
| FeCu-phenol (Fig. 8B)           | Redox species in the 2 <sup>nd</sup> sphere                           | $1.2 \times 10^5$                      | 11                      | 11   |
| FeFc4 (Fig. 8C)                 | Redox species + H-bond (2 <sup>nd</sup> sphere)                       | $5 \times 10^4$                        | 10                      | 35   |
| $Fc_3(CH_3Ph)$ -PorCo (Fig. 8D) | Electron donor groups in the 2 <sup>nd</sup> sphere                   |                                        | 100 (EEPG)              | 33   |
| FeL2 (Fig. 8E)                  | H-bond + protonated basic grp. (2 <sup>nd</sup> sphere)               | $1.80 \times 10^7$                     | 5                       | 26   |
| $Fe^{III}Cl$ -MARG (Fig. 2)     | H-bond + protonated basic grp. (2 <sup>nd</sup> sphere)               | $4.2 \times 10^6$                      | 18                      |      |
| Fe-MARG-N-Meimd (Fig. 8F)       | H-bond + protonated basic grp. (2 <sup>nd</sup> sphere) + push effect | $1.76 \times 10^6$                     | 7                       |      |

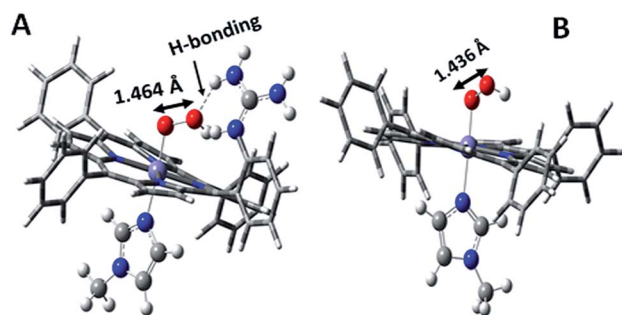


Fig. 9 DFT optimized structures of *N*-methylimidazole bound (A) protonated  $Fe^{III}$ -MARG hydroperoxide and (B)  $Fe^{III}$ -TPP hydroperoxide.

$Fe^{III}$ -OOH species show that the O-O bond in  $Fe^{III}$ -MARG is elongated to 1.46 Å relative to the 1.43 Å in  $Fe^{III}$ -TPP (Fig. 9). This weakening of the O-O bond is brought about by the H-bonding with the protonated guanidine group (1.45 Å in neutral guanidine, Fig. S13, ESI<sup>†</sup>). No accumulation of  $Fe^{III}$ -OOH species during the ORR as shown by the SERRS-RDE data is consistent with a fast O-O bond cleavage step. Note that the H-bonding to the guanidine results in 16 kcal mol<sup>-1</sup> stronger  $O_2$  binding on this site of the porphyrin relative to the open site, suggesting that the ORR is indeed likely to proceed on the side

bearing the guanidine (Fig. S14, ESI<sup>†</sup>). Thus, the H-bonding from the protonated guanidine activates the O-O bond for cleavage which results in enhancement in both the rate and selectivity of the ORR.

## Conclusion

In summary, inclusion of pendant guanidine groups in the iron porphyrin architecture, inspired by the Arg38 residue in the distal site of HRP, increases both the rate and selectivity of the electrocatalytic  $4e^-/4H^+$  oxygen reduction reaction in an aqueous environment. Inclusion of the axial imidazole ligand further enhances the selectivity of the oxygen reduction process producing minimal PROS. Thus, the inclusion of push and pull effects of the HRP active site in synthetic iron porphyrins enhances the rate as well as the selectivity of oxygen reduction substantially. The hydrogen bonding from the pendant guanidine group activates the O-O bond of hydroperoxide species and thus is responsible for the selectivity and rate enhancement observed here. *In situ* spectroscopy indicates the oxygen binding to iron step as the rds of the ORR process.

## Materials and methods

Details of the experimental procedure and materials are included in the ESI<sup>†</sup>.



## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research was funded by Department of Science and Technology Grant SERM/EMR/008063 and Council of Scientific and Industrial Research Grant (CSIR) No. 01(2874)/17/EMR-II. A. G. and S. B. thank UGC SRF and CSIR SPMF, respectively, and S. B. acknowledges IACS integrated Ph.D.

## Notes and references

- 1 Y.-H. Wang, Z. K. Goldsmith, P. E. Schneider, C. W. Anson, J. B. Gerken, S. Ghosh, S. Hammes-Schiffer and S. S. Stahl, *J. Am. Chem. Soc.*, 2018, **140**, 10890–10899.
- 2 W. Zhang, W. Lai and R. Cao, *Chem. Rev.*, 2017, **117**, 3717–3797.
- 3 J. P. Collman, R. A. Decréau, H. Lin, A. Hosseini, Y. Yang, A. Dey and T. A. Eberspacher, *Proc. Natl. Acad. Sci.*, 2009, **106**, 7320.
- 4 J. P. Collman, R. Boulatov, C. J. Sunderland and L. Fu, *Chem. Rev.*, 2004, **104**, 561–588.
- 5 S. M. Adam, G. B. Wijeratne, P. J. Rogler, D. E. Diaz, D. A. Quist, J. J. Liu and K. D. Karlin, *Chem. Rev.*, 2018, **118**, 10840–11022.
- 6 S. Dey, B. Mondal, S. Chatterjee, A. Rana, S. Amanullah and A. Dey, *Nat. Rev. Chem.*, 2017, **1**, 0098.
- 7 M. L. Rigsby, D. J. Wasylenko, M. L. Pegis and J. M. Mayer, *J. Am. Chem. Soc.*, 2015, **137**, 4296–4299.
- 8 S. Ferguson-Miller and G. T. Babcock, *Chem. Rev.*, 1996, **96**, 2889–2908.
- 9 T. Tsukihara, H. Aoyama, E. Yamashita, T. Tomizaki, H. Yamaguchi, K. Shinzawa-Itoh, R. Nakashima, R. Yaono and S. Yoshikawa, *Science*, 1996, **272**, 1136.
- 10 M. Svensson-Ek, J. Abramson, G. Larsson, S. Tornroth, P. Brzezinski and S. Iwata, *J. Mol. Biol.*, 2002, **321**, 329–339.
- 11 J. P. Collman, N. K. Devaraj, R. A. Decréau, Y. Yang, Y.-L. Yan, W. Ebina, T. A. Eberspacher and C. E. D. Chidsey, *Science*, 2007, **315**, 1565–1568.
- 12 S. Hematian, I. Garcia-Bosch and K. D. Karlin, *Acc. Chem. Res.*, 2015, **48**, 2462–2474.
- 13 S. Chatterjee, K. Sengupta, S. Hematian, K. D. Karlin and A. Dey, *J. Am. Chem. Soc.*, 2015, **137**, 12897–12905.
- 14 S. Chatterjee, K. Sengupta, B. Mondal, S. Dey and A. Dey, *Acc. Chem. Res.*, 2017, **50**, 1744–1753.
- 15 S. Chatterjee, K. Sengupta, S. Samanta, P. K. Das and A. Dey, *Inorg. Chem.*, 2015, **54**, 2383–2392.
- 16 J. C. Love, L. A. Estroff, J. K. Kriebel, R. G. Nuzzo and G. M. Whitesides, *Chem. Rev.*, 2005, **105**, 1103–1170.
- 17 E. D. C. Christopher, *Science*, 1991, **251**, 919–922.
- 18 K. Mittra, S. Chatterjee, S. Samanta and A. Dey, *Inorg. Chem.*, 2013, **52**, 14317–14325.
- 19 S. Samanta, K. Sengupta, K. Mittra, S. Bandyopadhyay and A. Dey, *Chem. Commun.*, 2012, **48**, 7631–7633.
- 20 K. Sengupta, S. Chatterjee, S. Samanta and A. Dey, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 8431.
- 21 K. Sengupta, S. Chatterjee and A. Dey, *ACS Catal.*, 2016, **6**, 6838–6852.
- 22 S. Mukherjee, M. Mukherjee, A. Mukherjee, A. Bhagi-Damodaran, Y. Lu and A. Dey, *ACS Catal.*, 2018, **8**, 8915–8924.
- 23 K. Sengupta, S. Chatterjee and A. Dey, *ACS Catal.*, 2016, **6**, 1382–1388.
- 24 S. Samanta, P. K. Das, S. Chatterjee, K. Sengupta, B. Mondal and A. Dey, *Inorg. Chem.*, 2013, **52**, 12963–12971.
- 25 K. Sengupta, S. Chatterjee, S. Mukherjee, S. G. Dey and A. Dey, *Chem. Commun.*, 2014, **50**, 3806–3809.
- 26 S. Bhunia, A. Rana, P. Roy, D. J. Martin, M. L. Pegis, B. Roy and A. Dey, *J. Am. Chem. Soc.*, 2018, **140**, 9444–9457.
- 27 S. Chatterjee, K. Sengupta, S. Samanta, P. K. Das and A. Dey, *Inorg. Chem.*, 2013, **52**, 9897–9907.
- 28 T. L. Poulos, *Chem. Rev.*, 2014, **114**, 3919–3962.
- 29 M. Gajhede, D. J. Schuller, A. Henriksen, A. T. Smith and T. L. Poulos, *Nat. Struct. Biol.*, 1997, **4**, 1032–1038.
- 30 E. Derat and S. Shaik, *J. Phys. Chem. B*, 2006, **110**, 10526–10533.
- 31 S. Bhakta, A. Nayek, B. Roy and A. Dey, *Inorg. Chem.*, 2019, **58**, 2954–2964.
- 32 G. I. Berglund, G. H. Carlsson, A. T. Smith, H. Szöke, A. Henriksen and J. Hajdu, *Nature*, 2002, **417**, 463–468.
- 33 R. Boulatov, J. P. Collman, I. M. Shiryayeva and C. J. Sunderland, *J. Am. Chem. Soc.*, 2002, **124**, 11923–11935.
- 34 C. E. D. Chidsey, *Science*, 1991, **251**, 919.
- 35 S. Samanta, K. Mittra, K. Sengupta, S. Chatterjee and A. Dey, *Inorg. Chem.*, 2013, **52**, 1443–1453.
- 36 K. Sengupta, S. Chatterjee, S. Samanta, S. Bandyopadhyay and A. Dey, *Inorg. Chem.*, 2013, **52**, 2000–2014.
- 37 L. Ye, Y. Fang, Z. Ou, S. Xue and K. M. Kadish, *Inorg. Chem.*, 2017, **56**, 13613–13626.
- 38 B. Sun, Z. Ou, D. Meng, Y. Fang, Y. Song, W. Zhu, P. V. Solntsev, V. N. Nemykin and K. M. Kadish, *Inorg. Chem.*, 2014, **53**, 8600–8609.
- 39 A. W. Schaefer, M. T. Kieber-Emmons, S. M. Adam, K. D. Karlin and E. I. Solomon, *J. Am. Chem. Soc.*, 2017, **139**, 7958–7973.

