



**2021 Pioneering Investigators issue: Guanidium-  
Functionalized Cationic Molecular Umbrellas as Antibacterial  
Agents**

Journal:	<i>Polymer Chemistry</i>
Manuscript ID	PY-COM-01-2021-000071.R1
Article Type:	Communication
Date Submitted by the Author:	10-Mar-2021
Complete List of Authors:	Chen, Ao; Shanghai Jiao Tong University, School of Biomedical Engineering Chen, Elliot; Rensselaer Polytechnic Institute, Materials Science and Engineering Palermo, Edmund; Rensselaer Polytechnic Institute, Materials Science and Engineering

# 2021 Pioneering Investigators issue: Guanidium-Functionalized Cationic Molecular Umbrellas as Antibacterial Agents

Ao Chen<sup>1</sup>, Elliot Chen<sup>2</sup>, and Edmund F. Palermo<sup>2,\*</sup>

1. School of Biomedical Engineering, Shanghai Jiao Tong University, Shanghai, China 200030
2. Materials Science and Engineering, Rensselaer Polytechnic Institute, 110 8<sup>th</sup> St, Troy NY, USA 12180

\*Email: palere@rpi.edu

## Abstract


We report the synthesis of cationic dendrons (1<sup>st</sup> and 2<sup>nd</sup> generations) with pendant alkyl chains of varying lengths ( $C_8$ ,  $C_{12}$ ,  $C_{14}$ ), which are classified as cationic molecular umbrellas. In each case, the dendron surface moieties were functionalized with guanidine groups, which are fully protonated in aqueous media of pH 7.4, lending cationic character to the solute. We found that these compounds are potent membrane-disrupting antibacterial agents with dose-dependent hemolytic activities. Confocal microscopy confirmed the permeabilization of *E. coli* and *S. aureus* cell membranes. A pyrene emission assay confirms that the dendrons are unimolecularly solvated at the concentrations relevant to their antibacterial activity, although they do aggregate at higher concentrations in aqueous buffer. Most importantly, when we compare the activity of these guanidinium-functionalized umbrellas to our previously published data on ammonium-functionalized analogues, we found no significant benefits to guanidinium relative to the ammoniums. The antibacterial activities are similar in all cases tested, and the highest selectivity index was found in the ammonium series, which stands in contrast to many other classes of antibacterial agents for which guanidinylation is typically associated with enhanced activity and selectivity.

The alarming rise of antibiotic drug-resistant bacterial infections worldwide has generated much interest in alternative methods to stem the spread of harmful pathogens in the community and in the clinic.<sup>1</sup> A broad range of antimicrobial synthetic polymer chemistries, which were developed as inexpensive and synthetically scalable mimics of host defense peptides (HDPs), have shown potentially promising antibacterial activity and biocompatibility, both *in vitro* and *in vivo*.<sup>2,3</sup> The mechanism of antibacterial activity is putatively membrane disruption, although immunomodulatory effects may also play a role.<sup>4</sup> Perhaps the most widely recognized molecular design principle for these materials is the concept of amphiphilic balance – judiciously optimized composition of cationic charge (which mediates electrostatic attraction to anionic lipids that are abundant in bacterial cell membranes) and hydrophobicity (which facilitates insertion into and disruption of the lipid bilayer).<sup>5</sup> In this context, designing macromolecules with controlled spatial arrangement of these two elements remains a challenge at the forefront of the field. The notion of “facial amphiphilicity” argues that cationic charge and hydrophobicity ought to be predisposed to occupy opposite faces of the molecule, since the lipid bilayer is an approximately planar interface, at least locally, with anionic groups on one side and hydrophobic tails on the other.<sup>6</sup> Many different approaches have been pursued in this vein, from random copolymers with conformational freedom to side chains containing facially-amphiphilic pendant units.<sup>7–10</sup> Our own group recently developed the first example of a cationic “molecular umbrella” in which a long alkyl chain is attached to a dendron with cationic terminal groups.<sup>11</sup> In that first attempt, we identified a lead composition with potent antibacterial activity in the low  $\mu\text{g/mL}$  concentration range and more than 1300-fold cell-type selectivity for bacteria versus mammalian cell membrane disruption.

The chemical structure of the cationic groups is known to be a major determinant of antibacterial and hemolytic activities in random copolymers.<sup>12,13</sup> A popular choice for the cationic moiety is a protonated primary ammonium, which is mostly cationic in neutral aqueous media by virtue of protonation.<sup>14</sup> Primary ammoniums, which are selected because they mimic Lysine residues that are abundant in HDPs, often show better cell-type selectivity when directly compared to the more conventional choice of quaternary ammonium salt (QAS) groups.<sup>15</sup> Furthermore, guanidinium moieties are also a popular choice, because they mimic Arginine residues also found in HDPs and are known to bind more strongly to phospholipid headgroups via a combination of Coulombic attraction and bidentate hydrogen bonding interactions.<sup>16–19</sup> These examples in the literature have shown enhancement of antibacterial activity in direct comparison between ammonium- and guanidinium-functionalized, although comparable<sup>20,21</sup> or reduction<sup>22</sup> of antimicrobials were reported after the guanidinylation of certain HDP-mimetic structures. Thus, we questioned whether converting our ammonium-functionalized cationic molecular umbrellas (described above) to guanidinium variants could further enhance their already outstanding activity.

Guanidinium-functionalized cationic molecular umbrellas were prepared by minor modifications to our previously published route (Scheme 1).<sup>11</sup> Detailed procedures and characterization data are provided in the ESI. Briefly,  $\beta$ -alanine was guanidinylated using diBoc-protected *S*-methylisothiourea in methanol with  $\text{K}_2\text{CO}_3$  and 4-dimethylaminopyridine (DMAP). Dendrons of 2,2-bis(hydroxymethyl)propionic acid (bis-MPA) containing pendant hydroxyl surface groups, as well as a long hydrophobic chain attached to the core, were then coupled to the Boc-protected guanidino propanoic acid

via standard *N,N'*-dicyclohexylcarbodiimide (DCC)/ DMAP chemistry, and finally were deprotected with neat trifluoroacetic acid (TFA). Synthesis of the variants containing C<sub>8</sub>, C<sub>10</sub>, and C<sub>14</sub> hydrophobic handles was successful for the 1<sup>st</sup> and 2<sup>nd</sup> generation dendrons. Attempts to functionalize the 3<sup>rd</sup> generation examples led to less than quantitative surface group conversion, which stalled at less than ~6 out of 8 functionalized surface groups in the best case. Moreover, these samples contained an intractable impurity that was challenging to remove. Presumably, the difficulty can be ascribed to the bulkiness of the doubly Boc-protected guanidine group, which crowds out the remaining unreacted -OH moieties presented on the dendron surface. Thus, we proceeded to characterize the 1<sup>st</sup> and 2<sup>nd</sup> generation dendrons as an initial screen. As our main goal of this work was to directly compare dendrons that only differ in terms of the source of cationic charge (guanidium versus ammonium), the question of how to obtain the 3<sup>rd</sup> generation dendron was considered unnecessary to that end, and was thus relegated such effort to our future work. The chemical structure of the 2<sup>nd</sup> generation dendrons with cationic guanidinium groups is given in Scheme 1.

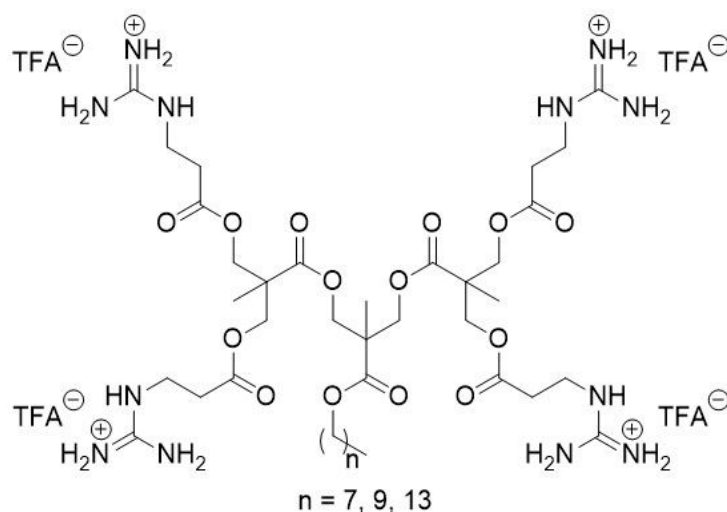

**Scheme 1.** Chemical structure of the G2 amphiphilic cationic molecular umbrellas that display guanidinium groups on the dendron surface and a long alkyl chain as the hydrophobic tail component.

Compounds in this work are denoted as C<sub>n</sub>G<sub>x</sub> where n is the number of carbons in the linear alkyl chain and x is the generation number of the dendron. For example, C<sub>14</sub>G<sub>2</sub> is the 2<sup>nd</sup> generation dendron attached to a -C<sub>14</sub>H<sub>29</sub> alkyl chain. The antimicrobial and hemolytic activities, along with characterization data, of all compounds in this study are listed in Table 1.

**Table 1.** Antibacterial (Minimum Inhibitory Concentration, MIC) and Hemolytic Activity (Hemolytic Concentration 50%, HC<sub>50</sub>), and critical micelle concentrations (CMC), for the Guanidine-Functionalized Cationic Molecular Umbrellas.

Cmpd.	Gen.	C <sub>n</sub>	MW (g/mol)	MIC (μg/mL)		HC <sub>50</sub> (μg/mL)	CMC (μg/mL)
				<i>E. coli</i> <sup>a</sup>	<i>S. aureus</i> <sup>b</sup>	RBC <sup>c</sup>	
<b>C<sub>8</sub>G<sub>1</sub></b>		8	701	250	500	438	>10,000
<b>C<sub>10</sub>G<sub>1</sub></b>	<b>G1</b>	10	729	62.5	62.5	279	9640
<b>C<sub>14</sub>G<sub>1</sub></b>		14	785	7.8	7.8	23	1170
<b>C<sub>8</sub>G<sub>2</sub></b>		8	1387	1000	250	1553	>10,000
<b>C<sub>10</sub>G<sub>2</sub></b>	<b>G2</b>	10	1415	62.5	62.5	327	1633
<b>C<sub>14</sub>G<sub>2</sub></b>		14	1471	7.8	7.8	117	201

<sup>a</sup> *E. coli* strain ATCC 25922

<sup>b</sup> *S. aureus* strain ATCC 25923


<sup>c</sup> Sheep red blood cells (RBC) obtained from MP biomedical

The antibacterial activities observed in the 1<sup>st</sup> generation dendron series, for which each compound contains just two protonated (cationic) guanidinium groups, are well in line with expectations based on the amphiphilic balance framework. While the C<sub>8</sub>G<sub>1</sub> compound showed weak activity (Minimum Inhibitory Concentration (MIC) values of 250 and 500 μg/mL for *E. coli* and *S. aureus*, respectively), increasing the hydrophobicity monotonically enhances antimicrobial potency. For example, as the alkyl chain length increased to C<sub>10</sub> chains, the antibacterial activity is enhanced (MIC 62.5 μg/mL for both strains) and further increasing to C<sub>14</sub> results in potent antimicrobial activity (MIC 7.8 μg/mL). Hemolytic activities against sheep red blood cells (RBC, MP Biomedicals) follow a similar trend, with hemolysis observed at lower concentrations for the more hydrophobic compounds. In Table 1, we list the Hemolytic Concentration 50% (HC<sub>50</sub>) values, which are widely considered the characteristic hemolytic concentrations (although some authors express a preference for the more conservative Hemolytic Concentration 10% (HC<sub>10</sub>) values). We include the entire hemolysis dose-response curves and curve fits to the modified Hill equation, in the ESI document so that any characteristic value one prefers may be extracted. In terms of selectivity between bacterial cells and RBCs, the 1<sup>st</sup> generation series is categorized as biocidal because the antibacterial and hemolytic activities are of similar magnitude in each case. In the 2<sup>nd</sup> generation series, for which four cationic guanidinium groups are displayed on each dendron, the trends for antibacterial activity are nearly the same as the 1<sup>st</sup> generation, but the hemolytic activities are less severe. The compound C<sub>14</sub>G<sub>2</sub> displayed the highest selectivity index in the series, albeit a relatively modest value (HC<sub>50</sub>/MIC = 15).

Analysis of aggregation in aqueous media was performed using a pyrene emission assay in the same manner as previously described.<sup>11</sup> Here, we define the critical micelle concentration (CMC) as the inflection point on the sigmoidal dose-response curves of I<sub>1</sub>/I<sub>3</sub> versus dendron concentration. Two observations are clear in the dataset. First, as expected, increasing hydrophobicity leads to aggregation in aqueous media at lower concentrations. Second, we also find in all cases that the CMC is higher than both the MIC and HC<sub>50</sub> values for a given example compound. Thus, we suggest that the active species is indeed individually solvated at the concentrations required to exert membrane

activity, rather than an aggregate or micelle assembled from these cationic surfactant molecules in solution. Plots are given in the ESI.

Confocal laser scanning microscopy was performed on *E. coli* and *S. aureus* treated with  $C_{14}G_2$  at concentrations of  $1 \times$  and  $4 \times$  MIC with SYTO-9 and Propidium iodide (PI) staining. The green SYTO9 stains all cells and the red PI only emits red when the membrane barrier function has been compromised. We find that untreated control *E. coli* sample shows the bacterial cells with smooth rod-like shape stained extensively with the green SYTO9, but with no significant red PI staining, indicative of all live cells (Figure 1, A and B). In contrast, treated *E. coli* cells showed a diminished green emission intensity with concomitant bright red emission, indicative of cell membrane permeabilization (Figure 1, C and D).

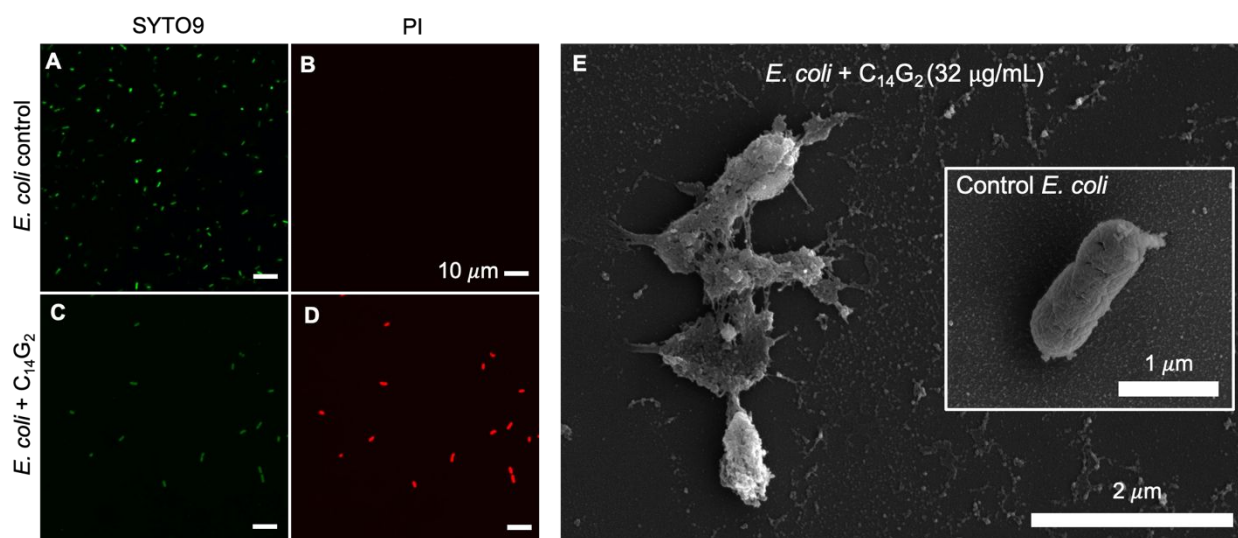


**Figure 1.** Confocal laser scanning microscopy images of (A, B) *E. coli* in PBS and (C, D) *E. coli* exposed to  $C_{14}G_2$  at  $32 \mu\text{g/mL}$  and (E) Scanning Electron Microscopy (SEM) images of *E. coli* exposed to  $C_{14}G_2$  at  $32 \mu\text{g/mL}$  compared to (inset) *E. coli* alone, both after fixation.

To further corroborate the notion of a membrane disruption mechanism with higher resolution images we also examined fixed *E. coli* cells by Scanning Electron Microscopy (SEM) as shown in Figure 1E. The untreated control sample (inset in Figure 1E) reveals the expected intact rod-shaped morphology of the *E. coli* cell. In contrast, the *E. coli* suspension incubated with  $32 \mu\text{g/mL}$  of  $C_{14}G_2$  shows gross disruption of cell shape, which is consistent with a direct mode of action against bacterial membranes.

Finally, we sought to directly compare the *guanidinium*-functionalized dendrons in this work to the previously described *ammonium*-functionalized dendrons<sup>11</sup> of our recent paper. Importantly, these structures are chemically identical except for the identity of the cationic group. To that end, we prepared a log-log plot of MIC versus  $HC_{50}$  with guidelines to represent regions of constant selectivity index (SI,  $HC_{50}/\text{MIC}$ ). From these data, we do not observe a clear or universal preference for ammonium or guanidinium surface groups on these cationic molecular umbrella type dendrons, at least for dendron generations 1 and 2. Although the trends are generally similar in both cases, there are some instances where the identity of the cationic charge appears to have a pronounced impact. For example, in the case of  $C_{10}G_2$ , the SI is nearly an order of magnitude higher when the

cationic groups are ammonium instead of guanidinium groups. In contrast, C<sub>8</sub>G<sub>1</sub> and C<sub>8</sub>G<sub>2</sub> both showed better SI for guanidinium, relative to ammonium groups, by about a factor of 3.

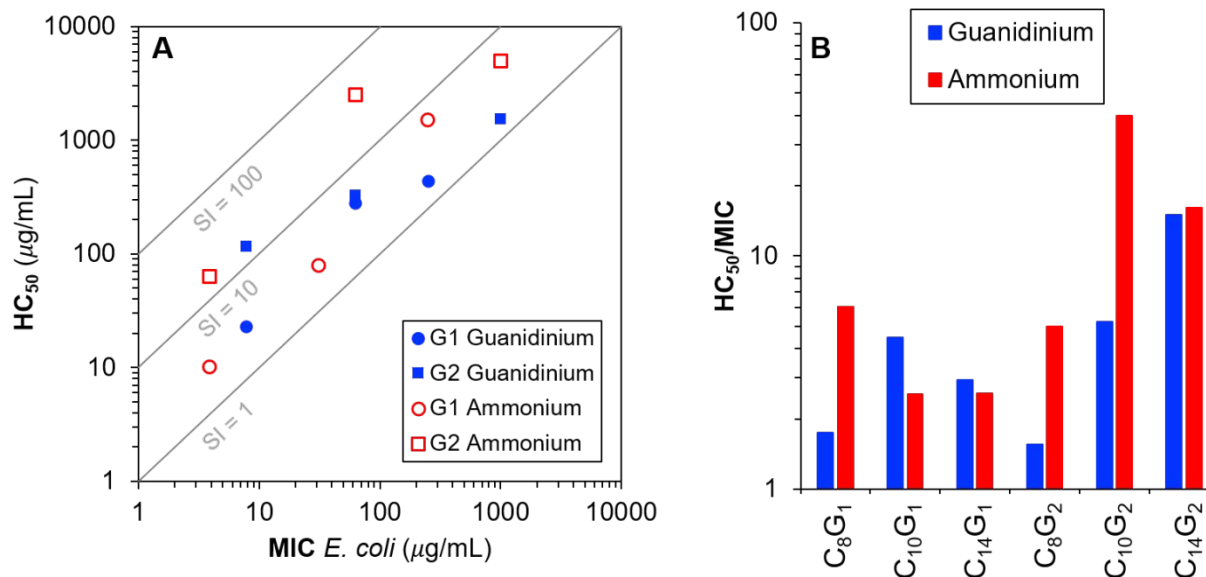

**Figure 2.** (A) Log-log Ashby plot of hemolytic activity against sheep red blood cells versus antimicrobial activity against *E. coli* and (B) bar chart of selectivity index, HC<sub>50</sub>/MIC, for the 1<sup>st</sup> and 2<sup>nd</sup> generation dendrons as a function of the chemical structure of their cationic charges.

In conclusion, this structure-activity relationship study revealed certain examples of biological activity in cationic molecular umbrellas that depends somewhat on the identity of the cationic groups (ammonium vs. guanidinium). However, guanidinylation of amines does not appear to universally enhance antibacterial activity or cell-type selectivity in the cationic umbrella design platform explored here. Indeed, another study from our laboratory, regarding the activity of photodynamic antibacterial oligothiophenes, also found that guanidinylation had only modest effects on activity.<sup>21</sup> Although much literature has been devoted to the development of guanidinium-rich antibacterial polymers as a method to enhance activity relative to ammonium-rich analogues, we have found that the effect is not necessarily universal. Overall, the highest cell-type selectivity in this small library screening effort was identified as C<sub>10</sub>G<sub>2</sub> with *ammonium* groups displayed on the dendron surface. In consideration of the contradictory effects of guanidinylation in other polymer systems, we suggest that such difference may result from the specific polymer structures. For molecular umbrellas, more effort will be focused on the structure-antibacterial behavior to better understand the difference in ammonium vs guanidinium functionalization in future investigations. Based on the available literature regarding synthetic mimics of cell-penetrating peptides,<sup>23</sup> these guanidinium containing molecular umbrellas should also be evaluated for their cytotoxicity and cell transfection efficiencies in future studies.

**Acknowledgements.** This work was supported in part by the National Science Foundation (Award #1653418). The donors of the American Chemical Society Petroleum Research Fund are gratefully acknowledged (57806-DNI7).



## References

- (1) Boucher, H. W. BAD BUGS, NO DRUGS 2002-2020: PROGRESS, CHALLENGES, AND CALL TO ACTION. *Trans. Am. Clin. Climatol. Assoc.* **2020**.
- (2) Ergene, C.; Yasuhara, K.; Palermo, E. F. Biomimetic Antimicrobial Polymers: Recent Advances in Molecular Design. *Polymer Chemistry*. 2018, pp 2407–2427. <https://doi.org/10.1039/c8py00012c>.
- (3) W. Scott, R.; N. Tew, G. Mimics of Host Defense Proteins; Strategies for Translation to Therapeutic Applications. *Curr. Top. Med. Chem.* **2016**, *17* (5), 576–589. <https://doi.org/10.2174/1568026616666160713130452>.
- (4) Brogden, K. A. Antimicrobial Peptides: Pore Formers or Metabolic Inhibitors in Bacteria? *Nature Reviews Microbiology*. March 2005, pp 238–250. <https://doi.org/10.1038/nrmicro1098>.
- (5) Palermo, E. F.; Lienkamp, K.; Gillies, E. R.; Ragogna, P. J. Antibacterial Activity of Polymers: Discussions on the Nature of Amphiphilic Balance. *Angew. Chemie* **2019**, *131* (12), 3728–3731. <https://doi.org/10.1002/ange.201813810>.
- (6) Tew, G. N.; Liu, D.; Chen, B.; Doerksen, R. J.; Kaplan, J.; Carroll, P. J.; Klein, M. L.; DeGrado, W. F. De Novo Design of Biomimetic Antimicrobial Polymers. *Proc. Natl. Acad. Sci. U. S. A.* **2002**. <https://doi.org/10.1073/pnas.082046199>.
- (7) Lienkamp, K.; Madkour, A. E.; Musante, A.; Nelson, C. F.; Nüsslein, K.; Tew, G. N. Antimicrobial Polymers Prepared by ROMP with Unprecedented Selectivity: A Molecular Construction Kit Approach. *J. Am. Chem. Soc.* **2008**. <https://doi.org/10.1021/ja801662y>.
- (8) Mowery, B. P.; Lee, S. E.; Kissounko, D. A.; Epand, R. F.; Epand, R. M.; Weisblum, B.; Stahl, S. S.; Gellman, S. H. Mimicry of Antimicrobial Host-Defense Peptides by Random Copolymers. *J. Am. Chem. Soc.* **2007**. <https://doi.org/10.1021/ja077288d>.
- (9) Zhou, Z.; Ergene, C.; Lee, J. Y.; Shirley, D. J.; Carone, B. R.; Caputo, G. A.; Palermo, E. F. Sequence and Dispersity Are Determinants of Photodynamic Antibacterial Activity Exerted by Peptidomimetic Oligo(Thiophene)S. *ACS Appl. Mater. Interfaces* **2019**, *11* (2), 1896–1906. <https://doi.org/10.1021/acsami.8b19098>.
- (10) Rahman, M. A.; Bam, M.; Luat, E.; Jui, M. S.; Ganewatta, M. S.; Shokfai, T.; Nagarkatti, M.; Decho, A. W.; Tang, C. Macromolecular-Clustered Facial Amphiphilic Antimicrobials. *Nat. Commun.* **2018**. <https://doi.org/10.1038/s41467-018-07651-7>.
- (11) Chen, A.; Karanastasis, A.; Casey, K. R.; Necelis, M.; Carone, B. R.; Caputo, G. A.; Palermo, E. F. Cationic Molecular Umbrellas as Antibacterial Agents with Remarkable Cell-Type Selectivity. *ACS Appl. Mater. Interfaces* **2020**, *12* (19), 21270–21282. <https://doi.org/10.1021/acsami.9b19076>.
- (12) Palermo, E. F.; Kuroda, K. Chemical Structure of Cationic Groups in Amphiphilic Polymethacrylates Modulates the Antimicrobial and Hemolytic Activities. *Biomacromolecules* **2009**, *10* (6), 1416–1428. <https://doi.org/10.1021/bm900044x>.
- (13) Palermo, E. F.; Vemparala, S.; Kuroda, K. Cationic Spacer Arm Design Strategy for Control of Antimicrobial Activity and Conformation of Amphiphilic Methacrylate Random Copolymers. *Biomacromolecules* **2012**, *13* (5), 1632–1641. <https://doi.org/10.1021/bm300342u>.
- (14) Gelman, M. A.; Weisblum, B.; Lynn, D. M.; Gellman, S. H. Biocidal Activity of Polystyrenes That Are Cationic by Virtue of Protonation. *Org. Lett.* **2004**. <https://doi.org/10.1021/ol036341+>.
- (15) Palermo, E. F.; Kuroda, K. Structural Determinants of Antimicrobial Activity in Polymers Which Mimic Host Defense Peptides. *Appl. Microbiol. Biotechnol.* **2010**, *87* (5), 1605–1615. <https://doi.org/10.1007/s00253-010-2687-z>.
- (16) Locock, K. E. S. Bioinspired Polymers: Antimicrobial Polymethacrylates. *Australian Journal of Chemistry*. 2016. <https://doi.org/10.1071/CH16047>.
- (17) Locock, K. E. S.; Michl, T. D.; Valentin, J. D. P.; Vasilev, K.; Hayball, J. D.; Qu, Y.; Traven, A.; Griesser, H. J.; Meagher, L.; Haeussler, M. Guanlylated Polymethacrylates: A Class of Potent Antimicrobial Polymers with Low Hemolytic Activity. *Biomacromolecules* **2013**. <https://doi.org/10.1021/bm401128r>.
- (18) Liu, D.; Choi, S.; Chen, B.; Doerksen, R. J.; Clements, D. J.; Winkler, J. D.; Klein, M. L.; DeGrado, W. F. Nontoxic Membrane-Active Antimicrobial Arylamide Oligomers. *Angew. Chemie Int. Ed.* **2004**, *43* (9), 1158–1162. <https://doi.org/10.1002/anie.200352791>.
- (19) Arias, M.; Piga, K.; Hyndman, M.; Vogel, H. Improving the Activity of Trp-Rich Antimicrobial Peptides by Arg/Lys Substitutions and Changing the Length of Cationic Residues. *Biomolecules*

- 2018**, *8* (2), 19. <https://doi.org/10.3390/biom8020019>.
- (20) Kohn, E.; Shirley, D.; Arotsky, L.; Picciano, A.; Ridgway, Z.; Urban, M.; Carone, B.; Caputo, G. Role of Cationic Side Chains in the Antimicrobial Activity of C18G. *Molecules* **2018**, *23* (2), 329. <https://doi.org/10.3390/molecules23020329>.
- (21) Zhou, Z.; Ergene, C.; Palermo, E. F. Guanidinium-Functionalized Photodynamic Antibacterial Oligo(Thiophene)S. *MRS Adv.* **2019**, *4* (59–60), 3223–3231. <https://doi.org/10.1557/adv.2019.359>.
- (22) Exley, S. E.; Paslay, L. C.; Sahukhal, G. S.; Abel, B. A.; Brown, T. D.; McCormick, C. L.; Heinhorst, S.; Koul, V.; Choudhary, V.; Elasri, M. O.; Morgan, S. E. Antimicrobial Peptide Mimicking Primary Amine and Guanidine Containing Methacrylamide Copolymers Prepared by Raft Polymerization. *Biomacromolecules* **2015**, *16* (12), 3845–3852. <https://doi.org/10.1021/acs.biomac.5b01162>.
- (23) deRonde, B. M.; Tew, G. N. Development of Protein Mimics for Intracellular Delivery. *Biopolymers* **2015**, *104* (4), 265–280. <https://doi.org/10.1002/bip.22658>.