



Delocalized Reduction of A-Site Ce in Ca-Ce-Ti-Mn Oxide Perovskites for Solar Thermochemical Applications

Journal:	<i>Energy & Environmental Science</i>
Manuscript ID	EE-ART-01-2023-000234.R1
Article Type:	Paper
Date Submitted by the Author:	20-Mar-2023
Complete List of Authors:	<p>Wexler, Robert; Princeton University, Department of Mechanical and Aerospace Engineering Sai Gautam, Gopalakrishnan; IISc, Materials Engineering Bell, Robert; National Renewable Energy Laboratory Shulda, Sarah; National Renewable Energy Laboratory Strange, Nicholas; Stanford Linear Accelerator Center Trindell, Jamie; Sandia National Laboratories California Sugar, Joshua; Sandia National Laboratories, Nygren, Eli; National Renewable Energy Laboratory Sainio, Sami; Stanford Synchrotron Radiation Lightsource McDaniel, Anthony H.; Sandia Labs, Ginley, David; National Renewable Energy Laboratory, Carter, Emily; Princeton University, Mechanical and Aerospace Engineering Stechel, Ellen; Arizona State University, LightWorks</p>

Broader context

Sunlight is an abundant albeit low areal density source of renewable energy. Collecting and concentrating the sun's rays for its heat value can enable high-temperature endothermic reactions such as water splitting to produce clean hydrogen. Two-step thermochemical cycles with redox-active metal oxides are promising. However, techno-economic analyses with state-of-the-art CeO_2 suggest that without a new active material, achieving the US Department of Energy's Hydrogen Shot \$1/kg H_2 target is unlikely. Here, we introduce a previously unknown material predicted from theoretical considerations and experimentally validated. The material is a redox-active quaternary oxide perovskite, CCTM, with solid solutions of Ca, Ce and Ti, Mn on the A- and B-sites, respectively. CCTM offers promising oxygen vacancy thermodynamics and exceptional H_2 yield, when reduced at moderate temperatures and cycled at relatively short reoxidation periods. Modeling reveals and experiment confirms that Ce^{4+} is the primary redox-active species, in contrast to other known reducible perovskites, where in all cases the active element sits on the B-site. Furthermore, even with B-site Ce^{4+} , that element is not redox active. Hence this work reports the first perovskite with reducible A-site, reducible Ce^{4+} , predicted entirely from theory, and subsequently validated with experiments that establish stability, reversibility, and high productivity.

Multiple and Nonlocal Cation Redox in Ca-Ce-Ti-Mn Oxide Perovskites for Solar Thermochemical Applications

Robert B. Wexler¹, Gopalakrishnan Sai Gautam^{1,2}, Robert T. Bell³, Sarah Shulda³, Nicholas A. Strange⁴, Jamie A. Trindell⁵, Joshua D. Sugar⁵, Eli Nygren^{3,6}, Sami Sainio⁴, Anthony H. McDaniel⁵, David Ginley³, Emily A. Carter^{1*}, and Ellen B. Stechel^{7*}

¹*Department of Mechanical and Aerospace Engineering and the Andlinger Center for Energy and the Environment, Princeton University, Princeton, NJ 08544-5263, United States*

²*Department of Materials Engineering, Indian Institute of Science, Bengaluru, Karnataka 560012, India*

³*National Renewable Energy Laboratory, Golden, CO 80401 United States*

⁴*SLAC National Accelerator Laboratory, Menlo Park, CA 94025 United States*

⁵*Sandia National Laboratories, Livermore, CA 94550, United States*

⁶*University of California Santa Cruz, Santa Cruz, CA 95064 United States*

⁷*ASU LightWorks® and the School of Molecular Sciences, Arizona State University, Tempe, Arizona 85287-8204, United States*

**Email: eac@princeton.edu, ellen.stechel@asu.edu*

Abstract

Modeling-driven design of redox-active off-stoichiometric oxides for solar thermochemical H₂ production (STCH) seldom has resulted in empirical demonstration of competitive materials. We report the theoretical prediction and experimental evidence that the perovskite Ca_{2/3}Ce_{1/3}Ti_{1/3}Mn_{2/3}O₃ is synthesizable with high phase purity, stable, and has desirable redox thermodynamics for STCH, with a predicted average neutral oxygen vacancy (V_O) formation energy, E_v=3.30 eV. Flow reactor experiments suggest potentially comparable or greater H₂ production capacity than recent promising Sr-La-Mn-Al and Ba-Ce-Mn metal oxide perovskites. Utilizing quantum-based modeling of a solid solution on both A and B sub-lattices, we predict the impact of nearest-neighbor composition on E_v and determine that A-site Ce⁴⁺ reduction dominates the redox-activity of Ca_{2/3}Ce_{1/3}Ti_{1/3}Mn_{2/3}O₃. X-ray absorption spectroscopy measurements provide evidence that supports these predictions and reversible Ce⁴⁺-to-Ce³⁺ reduction. Our models predict that Ce⁴⁺ reduces even when it is not nearest-neighbor to the V_O, suggesting that refinement of Ce stoichiometry has the possibility of further enhancing performance.

Main

Combating climate change calls for decarbonized production of H₂ that can provide cost-effective, medium-to long-duration energy storage while also serving as a fuel¹ for transportation or industrial products and processes, or a feedstock.² However, the vast majority (95%) of commercial H₂ is produced today via steam-methane reforming (SMR), which consumes fossil fuels and contributes to direct CO₂ emissions (≈ 7 kg CO₂ per kg H₂ for the overall process of SMR³). Water splitting (WS) via renewable energy offers a simpler, more direct path to clean hydrogen with exceptionally low carbon intensity, albeit currently at greater expense. Given the magnitude of solar irradiance on the Earth's surface, solar thermochemical hydrogen (STCH) is potentially a cost-effective, sustainable, and carbon-neutral pathway to H₂.⁴ However, functional STCH materials must meet an extraordinary set of requirements to be useful for large-scale hydrogen production. A STCH process that utilizes non-volatile metal oxides typically involves two steps,⁵ where the first is the thermal reduction (red) of a redox-active metal oxide (MO_x) at high temperatures generated by concentrated solar power⁶ or other solar sources of high-temperature heat and low partial pressures of oxygen (i.e., at T_{red} and pO₂ where $\Delta G_{\text{red}} \leq 0$). The second step is the re-oxidation (ox) of the reduced metal oxide by steam at lower temperatures (where T_{ox} is typically several hundred degrees K less than T_{red} for spontaneous WS), thereby generating hydrogen.⁵⁻⁷

Research over the last decade has struggled to replace pure CeO₂ as the state-of-the-art redox-active MO_x for two-step STCH.⁸⁻¹⁰ Thermal reduction of CeO₂-based redox-active materials leads to the formation of oxygen vacancies (V_O) and therefore off-stoichiometric compositions, (CeO_{2- δ}), which are re-occupied by O upon re-oxidation by steam.¹¹ However, demonstrated solar-to-fuel conversion efficiencies (η) have plateaued between 5-8%¹²⁻¹⁴ for laboratory-scale STCH reactors running on ceria at power levels < 5 kW_{thermal}. To surpass the performance of these CeO₂-based STCH reactors, researchers are exploring other redox-active metal oxides, with the ABO₃ perovskites being a popular choice due to their compositional and structural flexibility.¹⁵ Specifically, research over the last decade has identified Sr-La-Mn-Al¹⁶ and Ba-Ce-Mn¹⁷ oxide perovskites, among others, as potential next-generation redox-active MO_xs. However, metal-oxide perovskites have yet to supplant CeO₂-based materials as the preferred redox-active MO_x for STCH production.¹⁸

To create a stable and cyclable redox-active metal-oxide system at temperatures below the 1773 K needed for CeO₂ is a challenge. The metal oxide must have the correct thermodynamics to be able to cycle with steam as the oxidant, the kinetics to do so rapidly, and long-term stability at both the reduction and re-oxidation temperatures. To date, theory alone has yet to design new materials that cycle under conditions milder than necessary for CeO₂ with higher H₂ productivity. This paper provides and discusses validating evidence for a computational methodology that has been able to achieve that, identifying a new, highly functional STCH material.

Increasing the η of metal-oxide-perovskite-based STCH toward that of the ideal Carnot cycle generally amounts to optimizing the thermodynamics of both reduction and re-oxidation; or $\Delta G_{\text{red}} = \Delta H_{\text{red}} - T_{\text{red}} \Delta S_{\text{red}}$ and $\Delta G_{\text{ox}} = \Delta H_{\text{ox}} - T_{\text{ox}} \Delta S_{\text{ox}}$. For materials that undergo reduction via oxygen off-stoichiometry like CeO₂ and metal-oxide perovskites, V_O formation energies (E_v) of 3.4-3.9 eV correspond to optimal values of ΔH_{red} .¹⁹ The E_v of CeO₂ is too high (4.4 eV),⁴ hence the

need for the design of off-stoichiometry metal oxides like oxide perovskites with a lower E_v . Here, we build on our previous theoretical prediction of *Pnma* $\text{Ca}_{0.5}\text{Ce}_{0.5}\text{MnO}_3$ (CCM)²⁰ as a promising STCH candidate based on its E_v of 3.65-3.96 eV (within the target range¹⁹) and investigate a stabilized oxide perovskite with Ca and Ce on the A-site and Ti and Mn on the B-site.

Results

Computationally Predicted $\text{Ca}_{2/3}\text{Ce}_{1/3}\text{Ti}_{1/3}\text{Mn}_{2/3}\text{O}_3$ is Stable Experimentally

As is the convention in computational materials science, we quantify stability as the energy above the convex hull (E_{hull}), which is the energy change upon decomposition of a material into stable compounds at the same composition. Throughout, we performed density functional theory (DFT) calculations within the SCAN²¹+ U ²²⁻²⁵ framework (see **Section S1** and **Section S2** in the Supplemental information [SI] for additional details regarding the SCAN+ U calculations and E_{hull} computation, respectively).^{26,27} Based on this convex hull construction, CCM is thermodynamically metastable, with an $E_{\text{hull}} = 39$ meV/atom at 0 K. Experimental attempts to synthesize CCM perovskite were unsuccessful, with CeO_2 and Ca-Mn oxide phases predominating, and limited Ca-Ce-Mn oxide phase fraction decomposing during even gentle reduction (see **Section S3** in the SI). We then tried to increase the stability by using the naturally abundant and highly stable CaTiO_3 perovskite as a template to then add a solid solution of Ce^{4+} and Mn^{3+} on the A- and B-sites, respectively. Beginning with the previously predicted CCM, we increased the fraction of Ca on the A-site (from 1/2 to 2/3) and Ti on the B-sites (from 0 to 1/3). The resulting structure is a *Pnma* $\text{Ca}_{2/3}\text{Ce}_{1/3}\text{Ti}_{1/3}\text{Mn}_{2/3}\text{O}_3$ solid solution (CCTM2112, where the numbers indicate the relative composition of the material for three formula units or numerators of the fractional A- and B-site compositions for one formula unit), matching the *Pnma* structure of CaTiO_3 . For a preliminary check on stability, we used the τ tolerance factor of Bartel et al.²⁸ to predict whether CCTM2112 would form a perovskite. The τ value is 2.74, which gives a probability that the composition forms a perovskite structure of 94%, hence, high confidence. Additional support for this solid-solution approach came from reports of $\text{CaTi}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ ²⁹ and $\text{CaTi}_{0.2}\text{Mn}_{0.8}\text{O}_{3-\delta}$,³⁰ though, in our work, the A-site addition of Ce changes the predominant oxidation state of Mn in the fully-oxidized material from Mn^{4+} in the prior purely Ca-A-site perovskites to Mn^{3+} in CCTM2112 (see the section entitled **Role of Ce^{4+} in Redox Activity**). Independent simulation and empirical determination of the CCTM2112 crystal structure resulted in strong agreement in lattice parameters and atomic positions.

To simulate an experimentally realistic CCTM2112 solid solution, we constructed an optimized special quasirandom structure (SQS)^{31,32} with 360 atoms (216 of which are O atoms) and lattice constants of $a = 16.70$ Å, $b = 15.28$ Å, and $c = 16.13$ Å, corresponding to supercell dimensions of $3 \times 2 \times 3$, as shown in **Figure 1a** (where optimized refers to optimization of the lattice constants and to optimization of the particular SQS to mimic the random alloy). SCAN+ U calculations show that CCTM2112 has an $\approx 15\%$ lower E_{hull} ($= 33$ meV/atom, which is comparable to $k_B 298.15$ K ≈ 26 meV/atom) than the previously predicted CCM material, indicating improved stability. Other contributions to the stabilization of CCTM2112 probably include configuration entropy (which is > 41 meV/atom at 1273 K).²⁰ Additional details regarding the construction of the SQS for CCTM2112 (see **Figure S1** and **Figure S2**) can be found in **Section S4** of the SI.

We performed an independent experimental determination of the CCTM perovskite structure using bulk synthesis, powder X-ray diffraction (XRD) measurements, and Rietveld refinement. CCTM was synthesized with a bulk stoichiometry of $\text{Ca}_{0.65}\text{Ce}_{0.35}\text{Ti}_{0.3}\text{Mn}_{0.7}\text{O}_{3-\delta}$, approaching CCTM2112. Additional synthesis details can be found in **Section S3** of the SI. Structural refinements on the as-synthesized CCTM2112 powder using XRD data and the Rietveld method with no structural input from simulations. The XRD data and Rietveld refinement fit are shown in **Figure 1b**. For the CCTM phase, fractional occupancies of Ca, Ce, Ti, and Mn were initially allowed to refine, but did not deviate significantly from the initial 0.65-0.35-0.3-0.7 composition. No restraints were implemented since the solved structure was templated by an analogous GdFeO_3 -type structure ($Pnma$) and refined atomic positions readily converged. The final structural solution involved refinement of 30 structural parameters with weighted profile residual = 0.053 and goodness of fit equal to 0.22. Results of the CCTM phase refinement demonstrate clear random mixing of Ce and Ca on the A-site and Mn and Ti on the B-site. Figure 1b shows synchrotron XRD data for the CCTM powder, with the red ticks at the bottom denoting the positions of reflections simulated from the SCAN+U-computed CCTM2112 structure using the GSAS-II code.³³ The only impurity observed in the Rietveld refinement is < 1.2 wt.% CeO_2 (identified by bottom row of ticks in **Figure 1b**), which suggests a slight excess of A-site elements during synthesis and that all available Ca incorporates onto the A-site sublattice. The ≥ 98.8 wt.% CCTM phase fraction and ≥ 1773 K extended annealing temperature during synthesis confirm the high-temperature stability of CCTM. Additional structural details from the Rietveld refinement of the CCTM and CeO_2 phases are available in **Tables S1-S5** and **Section S6** of the SI.

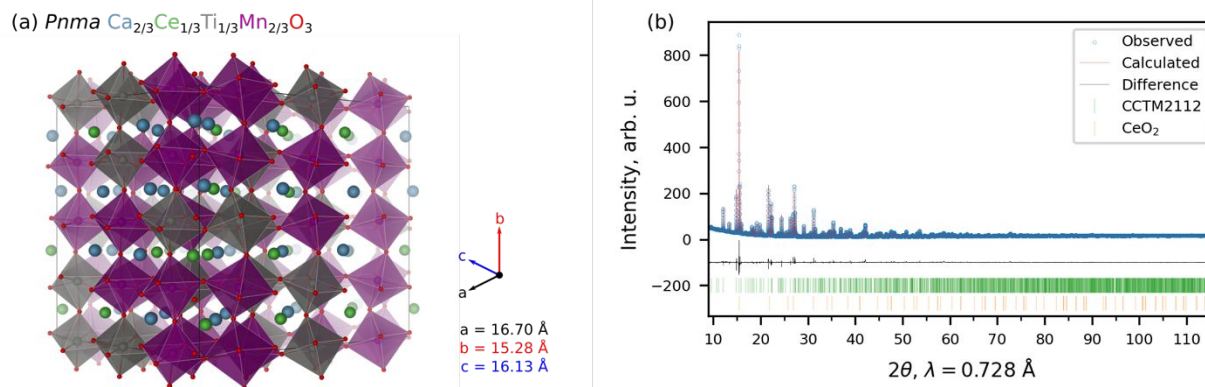


Figure 1. Crystal structure of CCTM2112. (a) SCAN+U-optimized SQS for $Pnma$ CCTM2112, where Ca, Ce, Ti, Mn, and O are blue, green, gray, purple, and red, respectively, and the polyhedra depict the B-site cations. Lattice constants (a , b , and c) are color-coded according to the axis labels. (b) Rietveld refinement of the as-synthesized CCTM powder. The green and orange tick marks, show the locations of CCTM and CeO_2 reflections, respectively.

Simulated and empirical determination of the CCTM crystal structure resulted in strong agreement. The evidence for this agreement is the comparison of the Rietveld refined $Pnma$ lattice parameters: $a = 5.61442 \text{ \AA} \pm 0.00013 \text{ \AA}$, $b = 7.55658 \text{ \AA} \pm 0.00018 \text{ \AA}$, $c = 5.35511 \text{ \AA} \pm 0.00013 \text{ \AA}$, to the simulated lattice parameters (extracted from supercell): $a = 5.567 \text{ \AA}$, $b = 7.640 \text{ \AA}$, and $c = 5.377 \text{ \AA}$, resulting in a deviation of simulation from empirical of -0.84% for a , +1.10% for b , and

+0.41% for c. Small differences are expected as the composition was not identical. Additional comparison of simulated and empirically derived CCTM unit cells are included in **Section S6.2** of the SI, which also shows an overlay of the computationally predicted structure onto the 300K XRD data (**Figure S3**).

$\text{Ca}_{2/3}\text{Ce}_{1/3}\text{Ti}_{1/3}\text{Mn}_{2/3}\text{O}_{3-\delta}$ Splits Water

We now examine the energetics of V_{O} formation in CCTM2112 and its dependence on the V_{O} 's nearest neighbors (NNs). Inspired by our recent finding that local chemistry governs V_{O} formation in ternary metal-oxide perovskites,³⁶ we categorized all 216 V_{O} s by their (NN) environment and randomly sampled one V_{O} (i.e., we introduce one V_{O} in the SQS, corresponding to $\delta = 0.014$) from each of the 13 unique V_{O} NN environments (**Figure 2a**). This categorization also gave a tractable number of SCAN+ U calculations from which to study the trends in the electronic and thermochemical properties of V_{O} s. We define NN V_{O} environments using x_{Ce} and x_{Mn} , where $x_{\text{Ce}} = N_{\text{Ce}} / (N_{\text{Ca}} + N_{\text{Ce}})$, $x_{\text{Mn}} = N_{\text{Mn}} / (N_{\text{Ti}} + N_{\text{Mn}})$, and x (N) is the fraction (number) of the V_{O} 's four NN A-sites and two NN B-sites occupied by Ce ($x_{\text{Ce}} = 1 - x_{\text{Ca}}$ and $N_{\text{Ce}} = 4 - N_{\text{Ca}}$) and Mn ($x_{\text{Mn}} = 1 - x_{\text{Ti}}$ and $N_{\text{Mn}} = 2 - N_{\text{Ti}}$), respectively. Note that the overall supercell structure maintains the same cation stoichiometry as that of bulk CCTM2112, with x_{Ce} and x_{Mn} in **Figure 2a** strictly defining compositions that are local to the V_{O} considered. Predictably, the V_{O} with the highest frequency ($f = 44$ or $44 / 216 \approx 20\%$ of the SQS) is the one with a NN environment closest to the bulk composition allowed by the A and B site NN fractions ($x_{\text{Ce}} = 0.25$ and $x_{\text{Mn}} = 0.5$ for the V_{O} and $x_{\text{Ce}} = \frac{1}{3}$ and $x_{\text{Mn}} = \frac{2}{3}$ for the bulk). Two NN V_{O} environments do not appear in the optimized SQS for CCTM2112 (namely those for $x_{\text{Ce}} = 1$ and $x_{\text{Mn}} \leq 0.5$), however, V_{O} s with these NN environments are unlikely to influence significantly the macroscopic reduction of CCTM2112 due to their scarcity ($x_{\text{Ce}} = 1$ and $x_{\text{Mn}} = 0.5$, and $x_{\text{Ce}} = 1$ and $x_{\text{Mn}} = 0$ make up 0.5% and 0.1% of the random alloy, respectively).

With this V_{O} categorization protocol, we predict that five of the 13 V_{O} s (shaded yellow and light blue in **Figure 2b**), including those with the first- and third-highest frequencies ($f = 44$ or $44/216 \approx 20\%$ for $x_{\text{Ce}} = 0.25$ and $x_{\text{Mn}} = 0.5$, which is 17.6% in a random solid (**Table S6**), and $f = 30$ or $30/216 \approx 14\%$ for $x_{\text{Ce}} = x_{\text{Mn}} = 0.5$, which is 13.2% of the sites in a random solid), have E_{v} s within (or within 0.06 eV of) the target range of 3.4-3.9 eV (see **Figure 2b**).¹⁹ To quantify the macroscopic reducibility of CCTM2112, we calculate the ensemble-averaged E_{v} , $\langle E_{\text{v}} \rangle = \sum_i f_i E_{\text{v},i} / \sum_i f_i$, where f_i is the frequency of the i^{th} unique NN V_{O} environment given in **Figure 2a**, and $\sum_i f_i = 216$. We obtain $\langle E_{\text{v}} \rangle = 3.30$ eV with a standard deviation of 0.36 eV based on the E_{v} values in **Figure 2b**, which overlaps with the target range for water splitting. We find that while E_{v} depends weakly on x_{Ce} , it systematically decreases with increasing x_{Mn} . This trend can be rationalized on the basis of crystal $\text{O}^{2-}\text{-M}^{n+}$ bond dissociation energies E_{b} , an extension of molecular O-M bond dissociation energies to the solid state,³⁶ defined as

$$E_{\text{b}}[\text{O}^{2-} - \text{M}^{n+}] = \frac{E_{\text{c}}[\text{MO}_{n/2}]}{N_{\text{b}}[\text{O}^{2-} - \text{M}^{n+}]} \quad (1)$$

where n is the oxidation state of the metal cation (M), $E_{\text{c}}[\text{MO}_{n/2}]$ is the cohesive energy of the ground-state polymorph of the binary metal-oxide crystal $\text{MO}_{n/2}$ containing M^{n+} , and $N_{\text{b}}[\text{O}^{2-}\text{-M}^{n+}]$ is the number of $\text{O}^{2-}\text{-M}^{n+}$ bonds per $\text{MO}_{n/2}$ formula unit. In short, $E_{\text{v}} \propto -x_{\text{Mn}}$ because $\text{O}^{2-}\text{-Mn}^{4+}$

(crystal bond dissociation energy $E_b = 2.25$ eV) and $O^{2-}-Mn^{3+}$ (1.97 eV) crystal bonds are weaker than $O^{2-}-Ti^{4+}$ (3.16 eV) and $O^{2-}-Ti^{3+}$ (2.62 eV).³⁶

Experiments demonstrate that CCTM2112 is a high-performance water splitter. The data presented in **Figure 2c** and **Figure 2d** were measured in a stagnation flow reactor dedicated to screening STCH materials.^{16,17} During dry redox cycling with O_2 (**Figure 2c**) the material is continuously exposed to ≈ 2000 ppm O_2 while heating from a base temperature of 1123 K to 1623 K. During heating (i.e., thermal reduction) the material evolves molecular oxygen as V_{OS} form in the crystal lattice, hence the positive rate of O_2 production. Upon cooling to 1123 K, the material uptakes an equivalent amount of O_2 from its surroundings as the V_{OS} are refilled, hence the negative rate of production. CCTM2112 is also redox active under the more stringent thermodynamic conditions of water splitting, as evidenced in **Figure 2d**. Here the sample is exposed to a high purity Ar sweep gas during thermal reduction followed by exposure to a mixture of 40 vol.% H_2O in Ar. As with O_2 redox, molecular oxygen is produced by thermal reduction. However, in the water splitting case, O atoms stripped from H_2O fill V_{OS} such that H_2 evolves in the presence of steam. Finally, when reduced a second and third time (after steam re-oxidation), an equivalent amount of O_2 evolves from the material at levels indicative of the first cycle. The δ calculated from the oxygen reduction in the flow reactor is $\delta = 0.06$, with the cycling $\Delta\delta = 0.05$. Due to different operating regimes, this δ for the flow reactor is approximately twice that of the soft XAS ($\delta = 0.033$, vide infra) and four times the modeling conditions (one vacancy per 360 atom structure or $\delta = 0.014$, vide supra). The data in **Figure 2d** demonstrates that CCTM2112 is reversibly redox active (for several cycles) in both O_2 and H_2O . Furthermore, the absolute amount of O_2 and H_2 produced during 40 vol.% steam cycling (area under blue curve = 10.4 mmol H_2 /mol atom CCTM2112) exceeds that of other high-performing perovskite compounds such as $BaCe_{0.25}Mn_{0.75}O_3$ (7.3 mmol H_2 /mol atom BCM) and $Sr_{0.4}La_{0.6}Mn_{0.6}Al_{0.4}O_3$ (8.2 mmol H_2 /mol atom SLMA), and CeO_2 (2.9 mmol H_2 /mol atom CeO_2) under similar experimental conditions (see **Section S5** in the SI for the calculation of the H_2 produced by these perovskite compounds). Note that CeO_2 does poorly under these conditions, e.g., compared with thermal reduction at ≈ 1800 K.⁸ In future work, we will pursue a more thorough comparison between all of these materials in the context of “high conversion,” which is re-oxidation in a less oxidizing environment, such as 1:1000 $H_2:H_2O$ in the oxidizing stream. Normalizing to mole atom (see **Section S5** for definition) makes these comparisons possible, without biasing one material over another.

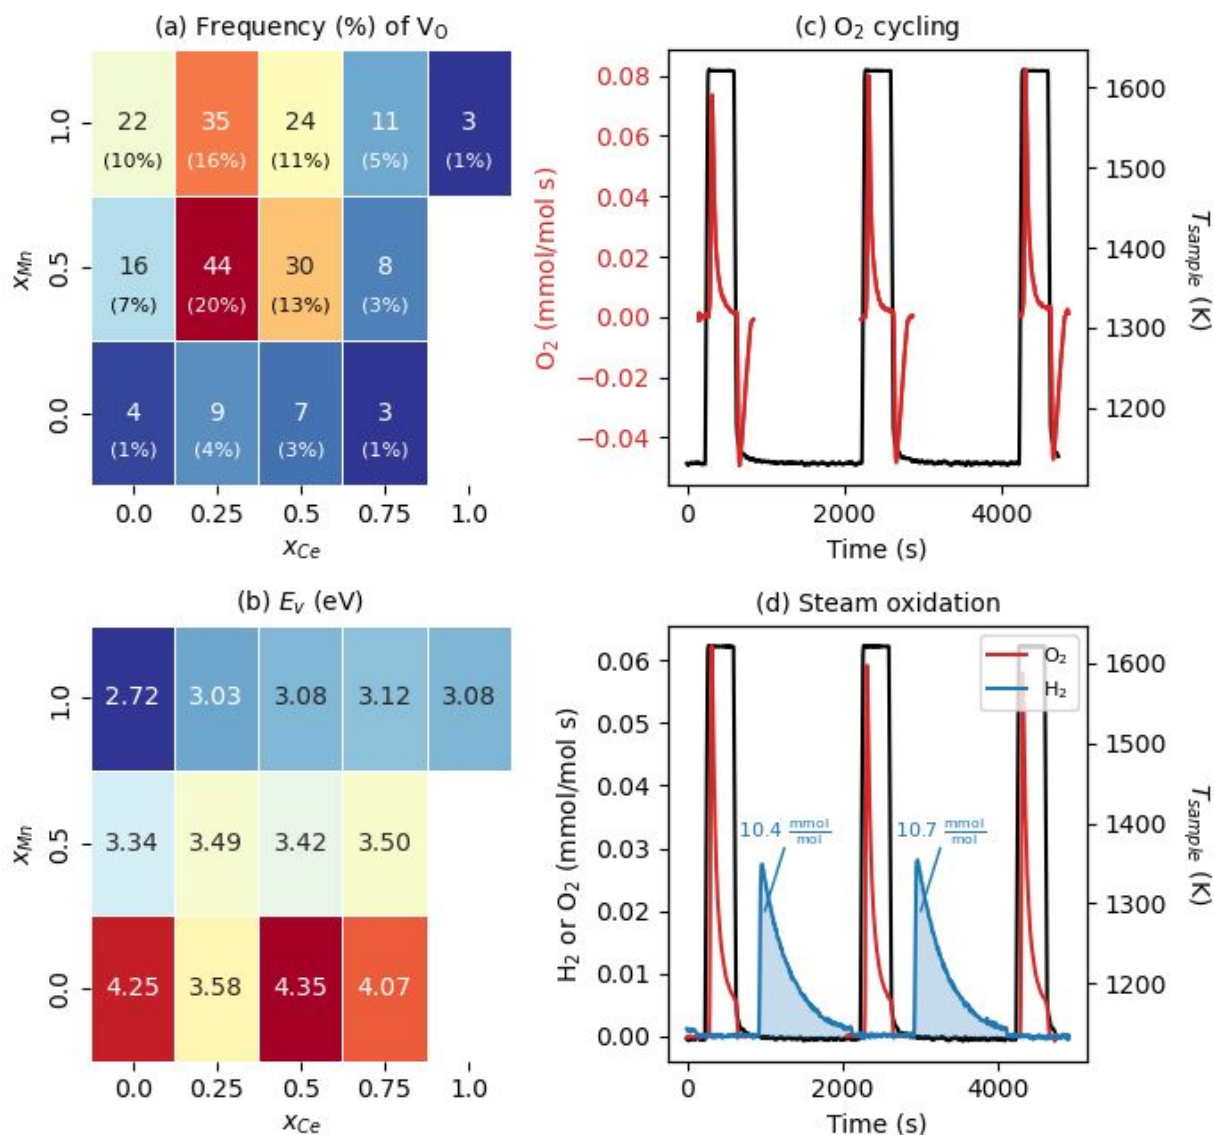


Figure 2. Water-splitting properties of CCTM2112. (a) Frequency (color of and text in rectangles) and probability (percentages in parentheses rounded to the nearest integer) of all unique NN V_O environments in the calculated CCTM2112 360-atom cell (and, in **Table S6**, for the random alloy), with dark red and dark blue shading indicating higher- and lower-frequency environments, respectively. (b) NN- V_O -environment dependence of calculated E_v in CCTM2112. Color of and text in rectangles correspond to E_v in eV, where the minimum $E_v = 2.72$ eV is dark blue and maximum $E_v = 4.35$ eV is dark red. (c) O_2 evolution rate normalized to mole atoms in CCTM2112 (see **SI Section S5** for definition) measured as a function of time during heating and cooling between 1123 K and 1623 K in a constant background of 2000 ppm oxygen. (d) O_2 and H_2 evolution rates normalized to mole atoms in CCTM2112 measured as a function of time during two successive redox cycles where the sample temperature is raised to 1623.15 K while sweeping with high purity Ar, followed by exposure to 40 vol% H_2O in Ar at 1123.15 K. The area under the gas evolution features in (c) and (d) is used to quantify the redox capacity of CCTM2112 during oxygen and steam oxidation.

Role of Ce⁴⁺ in Redox Activity

We aim to develop a mechanistic understanding of the high performance of CCTM2112 compared to the structurally related CTM and the Ce- and Mn-containing BCM perovskite water splitters. We therefore calculated and analyzed atomic magnetic moments (μ), which are extremely sensitive measures of oxidation- and spin-state changes. For fully oxidized CCTM2112, the mean magnetic moments in **Table 1** imply that, rounded to the nearest integer, the average oxidation states of Ca, Ce, Ti, Mn, and O are 2+, 4+, 4+, 3+, and 2-, respectively, which leads to a charge neutral formula unit (see **Figure S4** in the SI for the μ distributions). That said, Ce also can exist as Ce³⁺ and Mn as Mn⁴⁺ and Mn²⁺ (see min/max values in **Table 1**), where the latter suggests that disproportionation of two Mn³⁺ may occur in pristine CCTM2112.

To gain greater insight into the nature of the electronic reorganization in CCTM2112 upon V_O formation in the thermal reduction step of STCH, we computed the V_O-induced changes in the absolute values of μ_{Ce} , μ_{Mn} , and μ_{O} (use of absolute values controls for changes in relative orientation, i.e., ferromagnetic or antiferromagnetic; see **Figure S5** in the SI for a similar analysis of μ_{Ca} and μ_{Ti}). We then sum these $|\mu|$ changes separately for Ce, Mn, and O to quantify the extent to which the A, B, and O sub-lattices, respectively, are reduced (positive value) or oxidized (negative value) since changes in μ roughly correspond to changes in oxidation states, excluding Ca and Ti because we observe no more than marginal spin changes on these sites. Thus, the quantification of number of electrons added/removed from a species comes from our calculated changes in $|\mu|$. For example, when $x_{\text{Ce}} = 0$ and the change in $|\mu_{\text{Ce}}| \neq 0$, a V_O without a NN Ce has reduced a non-NN Ce, thus resulting in nonlocal or delocalized reduction.

Table 1. Magnetic moment summary statistics for fully oxidized CCTM2112. σ is the first standard deviation. All values are in μ_{B} . **Figure S4** in the SI shows the magnetic moment distributions.

Element	Mean $\pm \sigma$	Minimum	Maximum
Ca	0.00 \pm 0.00 (Ca ²⁺)	0.00 (Ca ²⁺)	0.00 (Ca ²⁺)
Ce	0.28 \pm 0.23 (Ce ⁴⁺)	0.06 (Ce ⁴⁺)	0.68 (Ce ³⁺)
Ti	0.05 \pm 0.02 (Ti ⁴⁺)	0.03 (Ti ⁴⁺)	0.08 (Ti ⁴⁺)
Mn	3.77 \pm 0.24 (Mn ³⁺)	3.10 (Mn ⁴⁺)	4.50 (Mn ²⁺)
O	0.01 \pm 0.01 (O ²⁻)	0.00 (O ²⁻)	0.05 (O ²⁻)

Our results show that reduction occurs primarily on the A-site Ce sub-lattice (**Figure 3a**) compared with that of Mn (**Figure 3b**) and O (**Figure 3c**), regardless of the V_O's NNs. In particular, the Ce sub-lattice reduces by 0.75 to 2.23 electrons depending on x_{Ce} and x_{Mn} , corresponding to an average decrease in Ce oxidation state of 0.031 to 0.093 e, respectively (average reduction of the 24 Ce in the unit cell); whereas, for Mn, no obvious net reduction or oxidation occurs during the formation of the V_O, with both mild reduction (≤ 0.35 electrons accepted) and oxidation (≤ 0.42 electrons donated) of Mn occurring simultaneously (see **Table S7** in the SI for a qualitative analysis of Ce and Mn oxidation state changes upon neutral V_O formation). During V_O formation, the remaining O sublattice experiences weak-to-mild reduction (≤ 0.52 electrons accepted in total by the O sub-lattice containing 216 atoms in the unit cell), reminiscent of the V_O-induced delocalized reduction of the O sub-lattice in the Sr₂Fe_{2-x}Mo_xO₆ double perovskites reported by

Muñoz-García et al.³⁷ The reduction of the O sub-lattice is indicative of empty O states in the pristine material, indicating that the Os are not fully ionized as O²⁻ (as seen by Bader charge analysis), with instead the M-O bonds exhibiting some singlet-coupled covalent character, which spin-averages the electrons on O to appear nonmagnetic.

X-ray absorption (XAS) synchrotron studies provide validating evidence supporting the predicted changes in average Ce and Mn oxidation states indeed occur during reduction of CCTM2112. We confirmed that, for oxidized CCTM2112 ($\delta \approx 0$), the predominant oxidation states of Mn and Ce are Mn³⁺ and Ce⁴⁺ by comparing the XAS spectrum of oxidized CCTM2112 (**Figure 3d** and **Figure 3e**) to standards. CCTM2112 was repeatedly reduced ($pO_2 \approx 1 \times 10^{-5}$ bar) and re-oxidized ($pO_2 \approx 0.2$ bar) in dry redox cycling conditions at 1473 K with 16 hours at each condition. CCTM2112 samples after both the third reduction and third re-oxidation were characterized. XRD confirms both the reduced and re-oxidized sample retained the CCTM structure with negligible secondary phase formation (**Figure S6**). Mass change in the sample between re-oxidizing and reducing conditions is consistent with a $\Delta\delta = 0.033 \pm 0.003$, with near full oxidation of the re-oxidized sample ($\delta \approx 0$) giving the reduced sample $\delta = 0.033 \pm 0.003$. In comparison, the one V_O out of 216 oxygen sites modeled here (**Figure 2**) corresponds to $\delta = 0.014$, conditions that are roughly half of the empirical reduction but still sufficiently close for comparing modeling results to observational data.

Soft XAS experiments at the Ce M-edge (i.e., X-ray-induced electron transitions from 3d to 4f orbitals) and Mn L-edge (electron transitions from 2p to 3d orbitals) were used to identify cation-specific changes in oxidation state. Increases in oxidation state result in less electron shielding of the atomic nucleus. Hence, more energy is required to excite a core electron, moving the spectrum edge position to higher energy. Ce and Mn oxidation states were benchmarked against known standards: CeO₂ for Ce⁴⁺, CeAlO₃ for Ce³⁺, MnO₂ for Mn⁴⁺, Mn₂O₃ for Mn³⁺, and MnO for Mn²⁺. The soft XAS results for the Ce M-edge (see **Figure 3d**) demonstrate reversible reduction of Ce (shift in edge positions at approximately 881 eV and 900 eV to lower energy upon reduction) to a fractional oxidation state of $\approx 3.90 \pm 0.03$, determined from a linear combination fit of the re-oxidized and reduced CCTM with the Ce⁴⁺ and Ce³⁺ standards (see **Figure S7** and **S8** in the SI). This measured 1.1% decrease in the average Ce oxidation state ($[4 - 3.9] / 4 = 2.5\%$ for $\delta = 0.033$, $\approx 2.5 \cdot 0.014 / 0.033 = 1.1\%$ for $\delta = 0.014$) agrees well with the 0.8% decrease predicted by SCAN+*U* calculations ($[(\langle q_{ox} \rangle) - (\langle q_{red} \rangle)] / \langle q_{ox} \rangle = [3.72 - 3.69] / 3.72 = 0.8\%$ for $\delta = 0.014$, where $\langle q \rangle$ is the ensemble-averaged Ce oxidation state). Additionally, the Mn L-edge (see **Figure 3e**) demonstrates no observable shift in edge positions (at approximately 641 eV and 652 eV), but does have evidence of Mn²⁺ oxidation to Mn³⁺ and Mn⁴⁺ reduction to Mn³⁺ (loss in intensity at the lower energy shoulder and higher energy side of the spectrum), supporting model predictions that simultaneous Mn oxidation and reduction occurs with modest net change in Mn oxidation state compared with that of Ce (see smaller values with positive and negative signs for Mn in **Figure 3b** compared with larger positive values for Ce in **Figure 3a**).

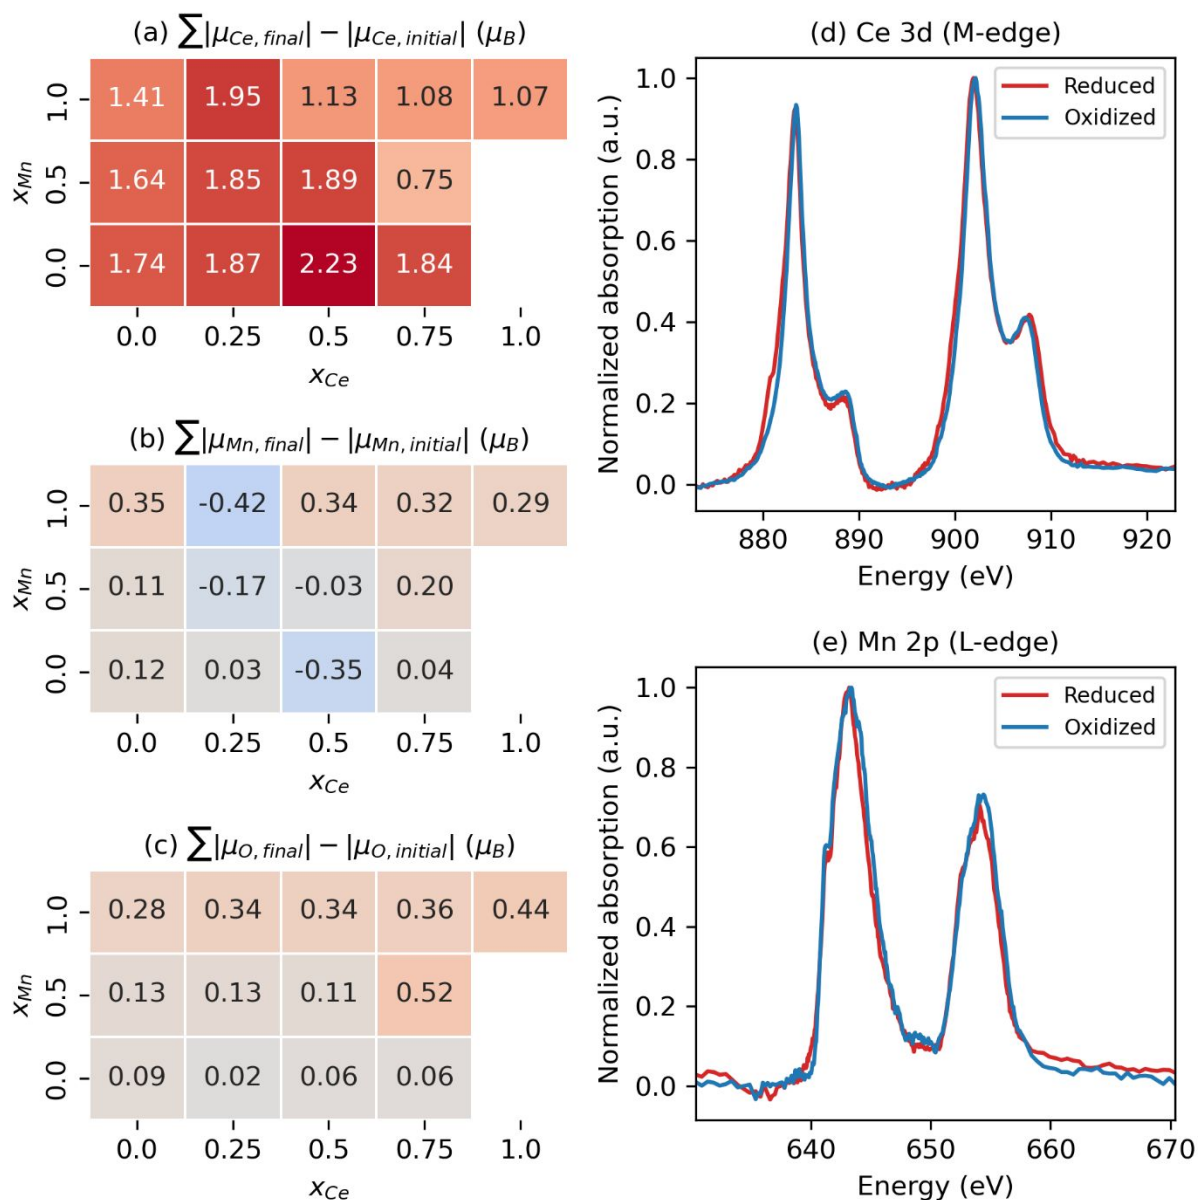


Figure 3. Multiple cation redox in CCTM2112. Dependence of V_O -induced absolute magnetic moment ($|\mu|$) changes for the (a) Ce, (b) Mn, and (c) O sub-lattices on the V_O 's NN environment, where the mole fractions, x , refer just to the NN environment. Note that we sum these $|\mu|$ changes separately for Ce, Mn, and O to quantify the extent to which the A, B, and O sub-lattices, respectively, are reduced (positive value) or oxidized (negative value) since μ changes roughly correspond to fractional oxidation state changes, reserving Ca and Ti for **Figure S5** in the SI because we observe marginal spin changes on these sites. XAS spectra at the (d) Ce $3d_{5/2}$ and (e) Mn $2p_{3/2}$ edge for reduced CCTM2112 and re-oxidized CCTM2112 (see **Figure S8** in the SI for the complete spectra).

Discussion

Nonlocal Ce Reduction

Surprisingly, we predict that Ce reduces even when it does not neighbor the V_O (see ≥ 1.41 electron reduction of the Ce sub-lattice for $x_{Ce} = 0$ in **Figure 3a**). To explore this phenomenon further, we study the spatial dependence of the $|\mu|$ changes induced by a V_O with a Ca- and Mn-rich local environment (i.e., $x_{Ce} = 0$ and $x_{Mn} = 1$). **Figure 4a** shows that two Ce reduce, labeled α ($\Delta|\mu| = 0.44 \mu_B$) and β ($0.53 \mu_B$), at distances of 4.32 \AA (for α) and 7.04 \AA (for β) from the V_O . Note that Ca and Ti are not redox active and only a few O are slightly reduced or become more ionic, mostly at distances of $< 5 \text{ \AA}$ from the V_O , which accounts for the non-zero value in **Figure 3c** for $x_{Ce} = 0$ and $x_{Mn} = 1$. Additionally, the Mn sub-lattice is both reduced and – to a slightly lesser extent – oxidized, leading to a net mild reduction of 0.35 electrons, corresponding to a disproportionation. Given the changes for Mn are modest, experimental validation is non-trivial. Ce reduction-at-a-distance also can be seen in **Figure 4b**, which displays the difference between the electron density (ρ) of CCTM2112 with and without (i.e., in its pristine state) this same neutral V_O ($\Delta\rho = \rho_{vacancy} - \rho_{pristine}$), as yellow isosurfaces (indicating electron gain) emerging from and surrounding the two green Ce labeled α and β , respectively. There are a lot of cyan isosurfaces as well, which implies, in the cases where $\Delta\rho$ is p -like, polarization rather than charge accumulation or depletion at those sites. This nonlocal reduction allows a substantial fraction of the Ce present in the material to participate in oxygen vacancy formation, and partially explains the high extent of Ce reduction in CCTM2112.

Having explored the spatial dependence of V_O -induced reduction, we now are able to explain the subtle x_{Ce} dependence of E_v at $x_{Mn} = 0$. The E_v for $x_{Ce} = 0$ (i.e., 4.25 eV) is the second highest value in **Figure 2b**, which we attribute to the localized reduction of Ce (\approx two Ce reduced in **Figure S9** of the SI), and the electrostatic penalty associated with its distance ($4.67\text{--}4.83 \text{ \AA}$) from the holes localized on the V_O (see, e.g., **Figure 4b**). For $x_{Ce} = 0.25$, the $E_v \approx 3.58 \text{ eV}$ (**Figure 2b**) is anomalously low because, while the reduction of Ce remains fairly localized (two Ce reduced at distances $< 5 \text{ \AA}$ to the V_O , **Figure S9**), these electrons are closer to the V_O -generated holes and therefore electrostatically stabilize the V_O . Note that strain can have an indirect effect on E_v by inducing or relaxing Jahn-Teller distortions on Mn but the strain effect is difficult to quantify.

Interestingly, E_v reaches its highest value for $x_{Ce} = 0.5$ (i.e., 4.35 eV ; **Figure 2b**), which we propose is the sum of (1) an electrostatic penalty for delocalized reduction of Ce (four Ce reduced by > 0.27 electrons at distances of 2.36 \AA to 9.48 \AA from the V_O , **Figure S9**) and the delocalized electrons' resultant screening of electron-hole interactions and (2) a penalty for oxidizing the Mn ($|\Delta\mu| = -0.55 \mu_B$) at a distance of 10.01 \AA from the V_O . Finally, from $x_{Ce} = 0.5$ to $x_{Ce} = 0.75$, E_v decreases from 4.35 eV to 4.07 eV (**Figure 2b**), which – considering the latter's fairly delocalized reduction of Ce (**Figure S9**) – seems to derive from the absence of oxidized Mn (i.e., Mn for which $\Delta|\mu| < 0 \mu_B$). Therefore, we can explain the subtle x_{Ce} dependence of E_v at $x_{Mn} = 0$ by the nature (localized/delocalized) and location of V_O -generated charge carriers interacting electrostatically with the V_O .

What Properties Promote the High Extent of Ce Reduction?

Lastly, it is worth discussing an interesting question that our results provoke: why does Ce^{4+} function as the primary acceptor of electrons (**Figure 3a**) if it is less reducible than Mn^{4+} and Mn^{3+} ? To quantify the reducibility of Ce^{4+} , Mn^{4+} , and Mn^{3+} , we calculate the enthalpy changes of the following solid-state reduction reactions: $\text{CeO}_2 \rightarrow 0.5 \text{Ce}_2\text{O}_3 + 0.25 \text{O}_2$, $\text{MnO}_2 \rightarrow 0.5 \text{Mn}_2\text{O}_3 + 0.25 \text{O}_2$, and $0.5 \text{Mn}_2\text{O}_3 \rightarrow \text{MnO} + 0.25 \text{O}_2$, respectively. Mn^{4+} is the most reducible cation ($\Delta H = 0.40$ eV) followed by Mn^{3+} ($\Delta H = 1.02$ eV) and then Ce^{4+} ($\Delta H = 1.82$ eV). Additionally, since these reactions are normalized per one-electron reduction, their ΔH s are effectively crystal reduction potentials (V_r), which are a key factor governing E_v in ternary oxide perovskites.³⁶ While this simple analysis suggests that Ce should not reduce, the unoccupied states closest to the Fermi level in metallic CCTM2112 are Ce 4*f* states (see **Figure S10** in the SI). Therefore, *even though Ce^{4+} is less reducible than Mn^{4+} and Mn^{3+} in their ground-state binary oxides, Ce does reduce in CCTM2112 because there is a lower energy penalty for the structure to put the V_O -donated electrons in the Ce 4*f* states, even if the Ce atom is physically farther from the V_O .* Ce^{4+} reduction is also accompanied by delocalization of electrons (due to the degeneracy of 4*f* states contributed by several Ce atoms close to the Fermi level), while Mn reduction is almost always local, evidenced by the presence or absence of Jahn-Teller distortions associated with Mn^{3+} . The need for 4*f* states near the Fermi level to reduce Ce^{4+} in the presence of Mn^{3+} is consistent with the observation that Mn and not Ce reduces during thermochemical cycling of $\text{Ba}(\text{Ce},\text{Mn})\text{O}_3$ (BCM) perovskites (where Ba is on the A-site, and Ce and Mn occupy the B-site)¹⁷ because BCM has a band gap and thus V_O -induced reduction is driven by cation proximity and reducibility rather than the relative location of unoccupied states near the Fermi level. Thus, the density of states for CCTM2112 promotes Ce reduction, revealing a mechanism that quantum-based modeling can target to predict other formulations of Ca-Ce-Ti-Mn-O as well as other materials with enhanced Ce reduction and thus enhanced STCH performance.

The high reducibility of Ce^{4+} in CCTM2112 is both key to its high water-splitting performance and substantially different than the behavior of CeO_2 and other previously demonstrated Ce^{4+} -containing off-stoichiometric redox-active materials. The existence of Ce^{4+} reduction is observed directly in both modeling and XAS. The most obvious structural distinction of CCTM2112 is the 12-fold coordination of Ce^{4+} on the A-site, compared to the 8-fold coordination of Ce^{4+} in the CeO_2 fluorite structure and 6-fold coordination on the B-site of BCM. As discussed above, the redox activity of Mn on the B-site is less clear, which suggests that other electronically similar elements may be able to substitute on the B-site and enable A-site Ce^{4+} reduction.²⁰ These results further suggest that a heretofore under-investigated family of Ce^{4+} A-site perovskites may exist with comparably high performance, across a range of alternate A-site and B-site elemental substitutions and ratios.

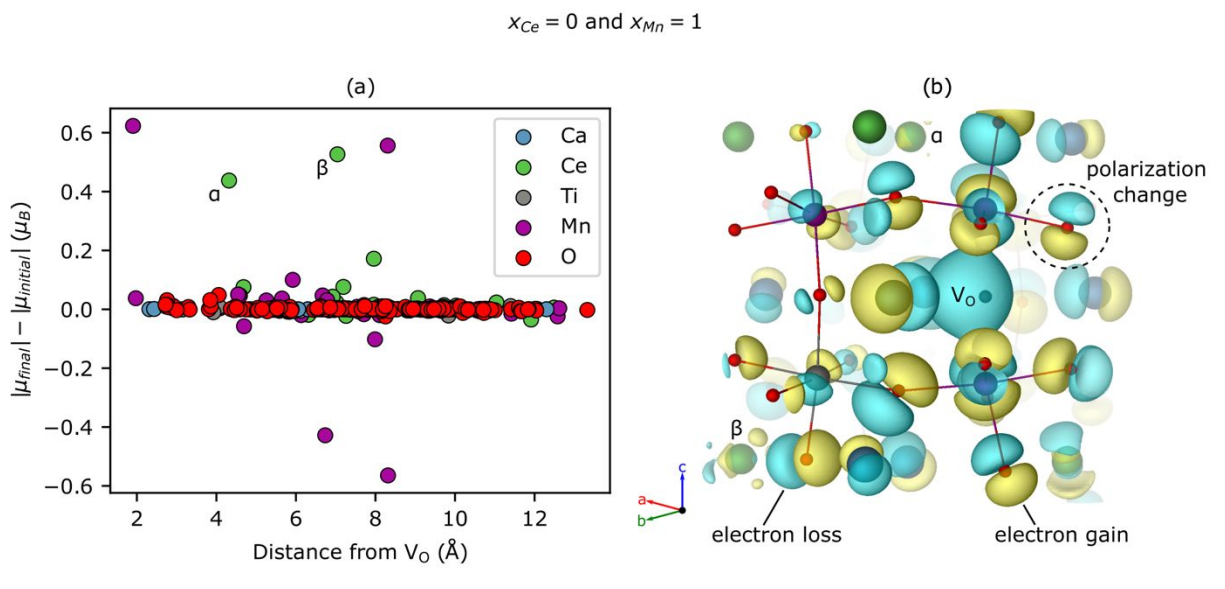


Figure 4. Nonlocal Ce reduction in CCTM2112 upon formation of a V_O in a Ca- and Mn-rich local environment ($x_{\text{Ce}} = 0$ and $x_{\text{Mn}} = 1$). (a) V_O -induced magnetic moment changes vs. distance, with two Ce (α and β) highlighted. (b) Electron density difference upon V_O formation, $\Delta\rho = \rho_{\text{vacancy}} - \rho_{\text{pristine}}$, where ρ_{vacancy} and ρ_{pristine} are the electron densities of CCTM2112 with and without the V_O . Isosurfaces correspond to a $\Delta\rho$ value of $0.06 \text{ e}/\text{\AA}^3$, with yellow and cyan isosurfaces corresponding to regions of electron gain and loss, respectively.

Conclusions

Perovskite $\text{Ca}_{2/3}\text{Ce}_{1/3}\text{Ti}_{1/3}\text{Mn}_{2/3}\text{O}_3$ (CCTM2112) offers potential to have greater solar thermochemical H_2 (STCH) production capacity than two other high-performing perovskite compounds, specifically $\text{Sr}_{0.4}\text{La}_{0.6}\text{Mn}_{0.6}\text{Al}_{0.4}\text{O}_3$ (SLMA4664) and $\text{BaCe}_{0.25}\text{Mn}_{0.75}\text{O}_3$ (BCM), and greater than CeO_2 at operating temperatures of 1623.15 K for the thermal reduction step and 1123.15 K for the water-splitting step. Additionally, the more general Ca-Ce-Ti-Mn-O phase space provides possibilities for supplanting CeO_2 -based materials as the preferred redox-active MO_x for STCH. Ce being the dominant acceptor of the electrons left behind by neutral oxygen vacancy formation, unlike other Ce-containing oxide perovskites for STCH like BCM, suggests that refinement of the Ce stoichiometry is a particularly promising avenue for future research. Finally, the electronic-structure-based mechanism that promotes Ce reduction with lower vacancy formation energies than in CeO_2 reveals novel physics and redox-active materials design considerations for realizing the climate-change-mitigation potential of STCH. As such, this work does not just introduce one high-performing material but instead uses the modeling-driven and experimentally verified discovery of a new water splitter with a distinct mechanism of action to introduce a new family of water-splitting materials.

Experimental Details

Synchrotron powder X-ray diffraction data were acquired at the Stanford Synchrotron Radiation Lightsource (SSRL), beam line 2-1. The incident X-ray wavelength used was 0.730 \AA as

determined by a refinement of data from a NIST 660C LaB₆ diffraction standard. CCTM powders were prepared in 0.028-inch outer diameter Kapton capillaries with 0.002-inch wall thickness and rotated (≈ 1 rotation per second) during data acquisition. 2D diffraction images were obtained with a Pilatus 100K hybrid photon counting detector, and subsequently integrated into a 1D pattern using a python script developed at SSRL for beam line 2-1. The diffraction pattern used to compare the experimental XRD data to the DFT model was simulated from the "CCTM2112" model, subjected to the ADDSYM routine within PLATON.³⁸ The XRD data was indexed using NTREOR, contained within the EXPO2014³⁹ suite of crystallographic tools. Rietveld refinements were performed using GSAS-II.³³

X-Ray absorption spectroscopy data was acquired at SSRL, beam line 10-1. For analysis of each sample, a thin layer of CCTM powder was spread on carbon tape. Total fluorescence yield spectra were obtained with a silicon diode AXUV100 detector at the Ce 3d and Mn 2p edges. A Mn reference spectrum was collected simultaneously with data collection at the Mn edge for all samples. Specific to this beamline, an agglomerate of chemical species resides permanently within the beam path for reference collection. The reference material does not contain Ce, so no Ce reference was available. However, the Mn references collected throughout the experiment well align ensuring the monochromator was stable and data could be directly compared. Data was analyzed with Igor Pro (Wavemetrics, Lake Oswego, Oregon, USA). For each spectrum, the average value of the pre-edge region is subtracted, and the spectrum normalized to the Mn 2p_{3/2} or Ce 3d_{5/2}. Powder CCTM2112 samples were redox cycled in a laser-heated stagnation flow reactor.^{16,17} Approximately 100 mg of sample is placed in a shallow, loosely packed bed within the stagnation plane of the reactor flow field such that transport of gaseous species to and from the sample surface is governed by 1-D diffusion. The reactor operates at 75 Torr and the sample environment (i.e., gas flow rate, gas composition, temperature, pressure) is fully controlled using appropriate hardware and software. The gas composition in the reactor effluent is measured by mass spectrometry at a rate ~ 4 Hz, which is important because the re-oxidation and reduction chemistries are inherently transient. Since the reactor flow field is well behaved, physical processes such as gas-phase dispersion, reactant mixing, and detector time lag that normally confound the extraction of material-specific behavior from the as-measured transient signal but easily resolved using numerical methods. One unique feature of the experimental system is the use of a 500-W, continuous-wave, near-IR laser to rapidly heat the material during thermal reduction. This heating method mimics the radiative environment encountered in an ultra-high temperature concentrating solar receiver and allows exploration of the effects of rapid thermal cycling, such as crystallographic and morphological instabilities, on macroscopic water splitting behavior.

Supporting Information

- Further details about the SCAN+*U* calculations, stability of CCTM2112, SQS construction for *Pnma* CCTM2112, V_O NN environment statistics, magnetic moment distribution by species in pristine CCTM2112, dependence of the V_O-induced magnetic moment changes by element on the V_O's NN environment, qualitative Ce and Mn oxidation state changes upon V_O formation, V_O-induced magnetic moment changes vs. distance, and projected density of states of pristine CCTM2112^{40–47}

- Additional synthesis details, comparison of H₂ produced by state-of-the-art redox-active perovskites, and XRD and XAS data from the reduced and re-oxidized CCTM powder
- Files containing crystal structures, total energies, magnetic moments, and projected densities of states are available at <https://dx.doi.org/10.17172/NOMAD/2022.07.20-1>

Acknowledgments

The authors gratefully acknowledge research support from the HydroGEN Advanced Water Splitting Materials Consortium, established as part of the Energy Materials Network under the U.S. Department of Energy, Office of Energy Efficiency and Renewable Energy, Fuel Cell Technologies Office, under Award Number DE-EE0008090. The authors also acknowledge the computational resources sponsored by the Department of Energy's Office of Energy Efficiency and Renewable Energy located at the National Renewable Energy Laboratory. The authors also thank Princeton University for computing resources. The National Renewable Energy Laboratory is operated by Alliance for Sustainable Energy, LLC, for the U.S. Department of Energy (DOE) under Contract No. DE-AC36-08GO28308. Sandia National Laboratories is a multi-mission laboratory managed and operated by National Technology and Engineering Solutions of Sandia, LLC, a wholly owned subsidiary of Honeywell International Inc, for the U.S. Department of Energy's National Nuclear Security Administration under contract DE-NA0003525. Use of the Stanford Synchrotron Radiation Lightsource, SLAC National Accelerator Laboratory, is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Contract No. DE-AC02-76SF00515. The authors thank Kevin Stone and J.R. Troxel for their skillful assistance in preparation for measurements performed at SSRL beam line 2-1. The views and opinions of the authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights.

References

1. BESAC Subcommittee on International Benchmarking. *Can the U.S. Compete in Basic Energy Sciences?* (Department of Energy Office of Science, 2021). at <https://science.osti.gov/-/media/bes/pdf/reports/2021/International_Benchmarking-Report.pdf>
2. Cheng, W.-H., de la Calle, A., Atwater, H. A., Stechel, E. B. & Xiang, Chengxiang. Hydrogen from sunlight and water: A side-by-side comparison between photoelectrochemical and solar thermochemical water-splitting. *ACS Energy Lett.* **6**, 3096–3113 (2021).

3. Soltani, R., Rosen, M. A. & Dincer, I. Assessment of CO₂ capture options from various points in steam methane reforming for hydrogen production. *Int. J. Hydrog. Energy* **39**, 20266–20275 (2014).
4. Bayon, A., de la Calle, A., Stechel, E. B. & Muhich, C. Operational Limits of Redox Metal Oxides Performing Thermochemical Water Splitting. *Energy Technol.* **n/a**, 2100222 (2021).
5. Steinfeld, A. Solar thermochemical production of hydrogen—a review. *Sol. Energy* **78**, 603–615 (2005).
6. Romero, M. & Steinfeld, A. Concentrating solar thermal power and thermochemical fuels. *Energy Environ. Sci.* **5**, 9234–9245 (2012).
7. Meredig, B. & Wolverton, C. First-principles thermodynamic framework for the evaluation of thermochemical H₂O- or CO₂-splitting materials. *Phys. Rev. B* **80**, 245119 (2009).
8. Chueh, W. C., Falter, C., Abbott, M., Scipio, D., Furler, P., Haile, S. M. & Steinfeld, A. High-Flux Solar-Driven Thermochemical Dissociation of CO₂ and H₂O Using Nonstoichiometric Ceria. *Science* (2010). doi:10.1126/science.1197834
9. Abanades, S. & Flamant, G. Thermochemical hydrogen production from a two-step solar-driven water-splitting cycle based on cerium oxides. *Sol. Energy* **80**, 1611–1623 (2006).
10. Scheffe, J. R. & Steinfeld, A. Oxygen exchange materials for solar thermochemical splitting of H₂O and CO₂: a review. *Mater. Today* **17**, 341–348 (2014).
11. Sai Gautam, G., Stechel, E. B. & Carter, E. A. A First-Principles-Based Sub-Lattice Formalism for Predicting Off-Stoichiometry in Materials for Solar Thermochemical Applications: The Example of Ceria. *Adv. Theory Simul.* **3**, 2000112 (2020).

12. Marxer, D., Furler, P., Takacs, M. & Steinfeld, A. Solar thermochemical splitting of CO₂ into separate streams of CO and O₂ with high selectivity, stability, conversion, and efficiency. *Energy Environ. Sci.* **10**, 1142–1149 (2017).
13. Lu, Y., Zhu, L., Agrafiotis, C., Vieten, J., Roeb, M. & Sattler, C. Solar fuels production: Two-step thermochemical cycles with cerium-based oxides. *Prog. Energy Combust. Sci.* **75**, 100785 (2019).
14. Haeussler, A., Abanades, S., Julbe, A., Jouannaux, J. & Cartoixa, B. Solar thermochemical fuel production from H₂O and CO₂ splitting via two-step redox cycling of reticulated porous ceria structures integrated in a monolithic cavity-type reactor. *Energy* **201**, 117649 (2020).
15. Kubicek, M., Bork, A. H. & Rupp, J. L. M. Perovskite oxides – a review on a versatile material class for solar-to-fuel conversion processes. *J. Mater. Chem. A* **5**, 11983–12000 (2017).
16. McDaniel, A. H., Miller, E. C., Arifin, D., Ambrosini, A., Coker, E. N., O’Hayre, R., Chueh, W. C. & Tong, Jianhua. Sr- and Mn-doped LaAlO_{3-δ} for solar thermochemical H₂ and CO production. *Energy Environ. Sci.* **6**, 2424–2428 (2013).
17. Barcellos, D. R., Sanders, M. D., Tong, J., McDaniel, A. H. & O’Hayre, R. P. BaCe_{0.25}Mn_{0.75}O_{3-δ}— a promising perovskite-type oxide for solar thermochemical hydrogen production. *Energy Environ. Sci.* **11**, 3256–3265 (2018).
18. Schächli, R., Rutz, D., Dähler, F., Muroyama, A., Haueter, P., Lilliestam, J., Patt, A., Furler, P. & Steinfeld, A. Drop-in fuels from sunlight and air. *Nature* **601**, 63–68 (2022).
19. Wexler, R. B., Stechel, E. B. & Carter, E. A. in *Sol. Fuels* (Wiley-Scrivener, 2022).

20. Sai Gautam, G., Stechel, E. B. & Carter, E. A. Exploring Ca-Ce-M-O (M = 3d Transition Metal) Oxide Perovskites for Solar Thermochemical Applications. *Chem. Mater.* **32**, 9964–9982 (2020).
21. Sun, J., Ruzsinszky, A. & Perdew, J. P. Strongly Constrained and Appropriately Normed Semilocal Density Functional. *Phys. Rev. Lett.* **115**, 036402 (2015).
22. Anisimov, V. I., Zaanen, J. & Andersen, O. K. Band theory and Mott insulators: Hubbard U instead of Stoner I . *Phys. Rev. B* **44**, 943–954 (1991).
23. Liechtenstein, A. I., Anisimov, V. I. & Zaanen, J. Density-functional theory and strong interactions: Orbital ordering in Mott-Hubbard insulators. *Phys. Rev. B* **52**, R5467–R5470 (1995).
24. Anisimov, V. I., Aryasetiawan, F. & Lichtenstein, A. I. First-principles calculations of the electronic structure and spectra of strongly correlated systems: the LDA+ U method. *J. Phys. Condens. Matter* **9**, 767–808 (1997).
25. Dudarev, S. L., Botton, G. A., Savrasov, S. Y., Humphreys, C. J. & Sutton, A. P. Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+ U study. *Phys. Rev. B* **57**, 1505–1509 (1998).
26. Sai Gautam, G. & Carter, E. A. Evaluating transition metal oxides within DFT-SCAN and SCAN+ U frameworks for solar thermochemical applications. *Phys. Rev. Mater.* **2**, 095401 (2018).
27. Long, O. Y., Sai Gautam, G. & Carter, E. A. Evaluating optimal U for 3d transition-metal oxides within the SCAN+ U framework. *Phys. Rev. Mater.* **4**, 045401 (2020).

28. Bartel, C. J., Sutton, C., Goldsmith, B. R., Ouyang, R., Musgrave, C. B., Ghiringhelli, L. M. & Scheffler, M. New tolerance factor to predict the stability of perovskite oxides and halides. *Sci. Adv.* **5**, eaav0693 (2019).
29. Qian, X., He, J., Mastronardo, E., Baldassarri, B., Yuan, W., Wolverton, C. & Haile, S. M. Outstanding Properties and Performance of $\text{CaTi}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$ for Solar-Driven Thermochemical Hydrogen Production. *Matter* **4**, 688–708 (2021).
30. Miller, J. E., Babiniec, S. M., Coker, E. N., Loutzenhiser, P. G., Stechel, E. B. & Ambrosini, A. Modified Calcium Manganites for Thermochemical Energy Storage Applications. *Front. Energy Res.* **10**, 774099 (2022).
31. Zunger, A., Wei, S.-H., Ferreira, L. G. & Bernard, J. E. Special quasirandom structures. *Phys. Rev. Lett.* **65**, 353–356 (1990).
32. Ångqvist, M., Muñoz, W. A., Rahm, J. M., Fransson, E., Durniak, C., Rozyczko, P., Rod, T. H. & Erhart, P. ICET – A Python Library for Constructing and Sampling Alloy Cluster Expansions. *Adv. Theory Simul.* **2**, 1900015 (2019).
33. Toby, B. H. & Von Dreele, R. B. *GSAS-II*: the genesis of a modern open-source all purpose crystallography software package. *J. Appl. Crystallogr.* **46**, 544–549 (2013).
34. Le Page, Y. Computer derivation of the symmetry elements implied in a structure description. *J. Appl. Crystallogr.* **20**, 264–269 (1987).
35. Le Page, Y. *MISSYM* 1.1 – a flexible new release. *J. Appl. Crystallogr.* **21**, 983–984 (1988).
36. Wexler, R. B., Gautam, G. S., Stechel, E. B. & Carter, E. A. Factors Governing Oxygen Vacancy Formation in Oxide Perovskites. *J. Am. Chem. Soc.* **143**, 13212–13227 (2021).

37. Muñoz-García, A. B., Ritzmann, A. M., Pavone, M., Keith, J. A. & Carter, E. A. Oxygen Transport in Perovskite-Type Solid Oxide Fuel Cell Materials: Insights from Quantum Mechanics. *Acc. Chem. Res.* **47**, 3340–3348 (2014).
38. Spek, A. L. Structure validation in chemical crystallography. *Acta Crystallogr. D Biol. Crystallogr.* **65**, 148–155 (2009).
39. Altomare, A., Cuocci, C., Giacovazzo, C., Moliterni, A., Rizzi, R., Corriero, N. & Falcicchio, A. EXPO2013 : a kit of tools for phasing crystal structures from powder data. *J. Appl. Crystallogr.* **46**, 1231–1235 (2013).
40. Deml, A. M., Holder, A. M., O’Hayre, R. P., Musgrave, C. B. & Stevanović, V. Intrinsic Material Properties Dictating Oxygen Vacancy Formation Energetics in Metal Oxides. *J. Phys. Chem. Lett.* **6**, 1948–1953 (2015).
41. Kresse, G. & Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **47**, 558–561 (1993).
42. Kresse, G. & Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **54**, 11169–11186 (1996).
43. Blöchl, P. E. Projector augmented-wave method. *Phys. Rev. B* **50**, 17953–17979 (1994).
44. Kresse, G. & Joubert, D. From ultrasoft pseudopotentials to the projector augmented-wave method. *Phys. Rev. B* **59**, 1758–1775 (1999).
45. Ong, S. P., Richards, W. D., Jain, A., Hautier, G., Kocher, M., Cholia, S., Gunter, D., Chevrier, V. L., Persson, K. A. & Ceder, G. Python Materials Genomics (pymatgen): A robust, open-source python library for materials analysis. *Comput. Mater. Sci.* **68**, 314–319 (2013).

46. Ong, S. P., Wang, L., Kang, B. & Ceder, G. Li-Fe-P-O₂ Phase Diagram from First Principles Calculations. *Chem. Mater.* **20**, 1798–1807 (2008).
47. Ong, S. P., Jain, A., Hautier, G., Kang, B. & Ceder, G. Thermal stabilities of delithiated olivine MPO₄ (M=Fe, Mn) cathodes investigated using first principles calculations. *Electrochem. Commun.* **12**, 427–430 (2010).