CrystEngComm



PAPER

View Article Online View Journal | View Issue



Cite this: CrystEngComm, 2023, 25, 2119

Modulated self-assembly of hcp topology MOFs of Zr/Hf and the extended 4,4'-(ethyne-1,2-diyl) dibenzoate linker†

Sophia S. Boyadjieva,^a Francesca C. N. Firth, ^D Mohammad R. Alizadeh Kiapi,^c David Fairen-Jimenez, ^D Sanliang Ling, ^D Matthew J. Cliffe ^D *e and Ross S. Forgan ^D *a

Careful control of synthetic conditions can enhance the structural diversity of metal-organic frameworks (MOFs) within individual metal-linker combinations. Herein, we show that hcp topology MOFs of both Zr(IV) and Hf(IV), linked by the extended (ethyne-1,2-diyl)dibenzoate linker, can be prepared by modulated self-assembly. The controlled addition of acetic acid and water to solvothermal syntheses is essential to generate these phase pure hcp topology materials, which are characterised experimentally and computationally. The central alkyne unit of the linker can be quantitatively brominated, but this results in partial degradation of the hcp phase, in contrast to the more stable fcu topology analogues. Nevertheless, the MOFs represent new members of the hcp topology isoreticular series showing high crystallinity and porosity, and demonstrate that new materials can be discovered in existing MOF phase spaces through judicious adjustment of key synthetic parameters.

Received 10th November 2022, Accepted 26th February 2023

DOI: 10.1039/d2ce01529c

rsc.li/crystengcomm

Introduction

Metal-organic frameworks (MOFs) comprise metal ion or metal cluster nodes (also referred to as secondary building units, or SBUs) connected by multitopic organic ligands into multidimensional network structures. To date, it is estimated that over 100 000 MOF structures have been deposited in the Cambridge Structural Database, with this huge number attributed to the chemical diversity in the choice of both metal SBU and organic ligand. In addition, it is possible to isolate multiple phases from the same metal-ligand combination—topological diversity—by careful control of reaction parameters. A pertinent example is that of trivalent metals linked by linear ditopic dicarboxylates, which can yield structurally rigid (MIL-101) and flexible (MIL-88 and MIL-53) phases. Furthermore, we have also previously shown that, in

the specific case of Fe(III) MOFs with 1,4-benzenedicarboxylate (BDC $^{2-}$), coordination modulation—the addition of reagents to MOF syntheses that can tune the coordination and pH equilibria during self-assembly 6 —is a viable strategy for kinetically selecting a specific material from a complex phase landscape. 7

The multiple series of MOFs comprising Zr(v) or Hf(v) SBUs connected by linear ditopic dicarboxylate ligands present a particularly striking case study into the isolation of different MOF phases via synthetic control. Predominant among MOFs prepared from Zr(v) or Hf(v) and BDC^{2-} or its derivatives is the UiO-66 series, in which $[M_6(\mu_3\text{-O})_4(\mu_3\text{-OH})_4(RCO_2)_{12}]$ metal clusters (M=Zr,Hf,Fig.1a) are connected by twelve linear dicarboxylate linkers in a face-centred cubic (fcu) topology MOF (Fig. 1b). UiO-66(Zr) specifically exhibits the ideal formula $[Zr_6O_4(OH)_4(BDC)_6]$, and a wide range of isoreticular derivatives of these materials, including interpenetrated UiO-66 topology phases, have been reported with both longer and functionalised linkers.

Varying the reaction composition can also affect the resultant MOF structure. For example, changing the metal source from ZrCl₄ to Zr(ⁱOPr)₄ has led to the discovery of a polymorph of UiO-66 with a different connectivity and **hex** topology. Addition of monotopic carboxylic acids as coordination modulators has induced formation of "defect" phases where the modulators themselves are incorporated as charge-compensating defects. Such defect phases can form in

^a WestCHEM School of Chemistry, University of Glasgow, Joseph Black Building, University Avenue, Glasgow G12 8QQ, UK. E-mail: ross.forgan@glasgow.ac.uk ^b Yusuf Hamied Department of Chemistry, University of Cambridge, Cambridge CB2 1EW, UK

^c The Adsorption & Advanced Materials Laboratory (A2ML), Department of Chemical Engineering & Biotechnology, University of Cambridge, Philippa Fawcett Drive, Cambridge CB3 0AS, UK

^d Advanced Materials Research Group, Faculty of Engineering, University of Nottingham, University Park, Nottingham NG7 2RD, UK

^e School of Chemistry, University of Nottingham, University Park, Nottingham, NG7 2RD, UK. E-mail: matthew.cliffe@nottingham.ac.uk

[†] Electronic supplementary information (ESI) available. See DOI: https://doi.org/ 10.1039/d2ce01529c

Paper

Fig. 1 Comparison of the fcu and hcp topology MOFs adopted by tetravalent metals and linear dicarboxylate linkers, specifically focussing on those of Hf(w) and biphenyl-4,4'-dicarboxylate (BPDC). a) The [Hf₆(μ_3 -O)₄(μ_3 -OH)₄(RCO₂)₁₂] SBU. b) A section of the packing structure of fcu topology [Hf₆O₄(OH)₄(BPDC)₆], also known as UiO-67(Hf). c) The [Hf₁₂(μ_3 -O)₈(μ_3 -OH)₈(μ_2 -OH)₆(RCO₂)₁₈] SBU. d) A section of the packing structure of hcp topology [Hf₁₂O₈(OH)₁₄(BPDC)₉]. Hf: blue spheres (or, demonstrating Hf coordination environments in SBUs, polyhedra); C: grey; O: red. H atoms omitted for clarity.

MOFs with the linker 2,6-naphthalenedicarboxylate, where the connectivity of the hexanuclear SBU is reduced by the presence of charge-capping, monotopic acetate units.¹⁷ Modulated synthesis can even lower the connectivity of the structure in an ordered manner, as seen in the formation of reo UiO-66, which can be described as a missing cluster defect phase, where modulator incorporation (for example formic acid) leads to eight-connected SBUs that form welldefined nanodomains of the missing-cluster defect phase reo within the bulk of fcu UiO-66. 18,19 Increasing reaction temperatures leads to the MIL-140 series of MOFs phase, which have an infinite one-dimensional chain SBU.20 MIL-140A, linked by BDC²⁻, is representative of the isoreticular series, having overall formula [ZrO(BDC)]. It is suggested that the presence of a condensed 1-D chain SBU and its isolation at higher reaction temperatures means that MIL-140A is the thermodynamic phase and UiO-66 is a kinetic product,²⁰ although addition of water to syntheses promotes UiO-66 formation.21

Further careful synthetic control²² enables the synthesis of MOFs with higher nuclearity Zr(IV) or Hf(IV) SBUs linked by ditopic dicarboxylates. 23-27 For example, MOFs containing the condensed $[M_{12}(\mu_3-O)_8(\mu_3-OH)_8(\mu_2-OH)_6(RCO_2)_{18}]$ SBU (Fig. 1c) and adopting the hcp topology (Fig. 1d) have been reported with a range of linkers, including BDC2- and derivatives, 28-33 functionalised 1,4-naphthalenedicarboxylate, 29 and longer linkers such as biphenyl-4,4'-dicarboxylate, 23,30,34 1,1':4',1"-terphenyl-4,4"dicarboxylate, 35,36 4,4'-di(4-benzoato)-2,2'-bipyridine, 37 and 5,15-di(p-benzoato)porphyrin.³⁸ An example using

poly(ethylene terephthalate) as the source of the BDC^{2-} linker via direct synthesis has also been described. ³⁹ Individual systems have also been shown to undergo delamination by sonication, forming a hexagonal layered (hxl) phase and eventually hexagonal nanosheets (hns), ²³ which can also in specific cases be directly synthesised themselves. ³⁰

The hcp topology MOFs have been increasingly studied due to potential applications in luminescence, 29 water catalysis, 32,33,35 remediation,31 heterogeneous photocatalysis,³⁷ nanomedicine,38 and molecular separations.³⁹ Herein, we describe the synthesis and characterisation of Zr(IV) and Hf(IV) analogues of the hcp phase MOF linked by 4,4'-(ethyne-1,2-diyl)dibenzoate (EDB²⁻), which we have termed GUF-12 (GUF = Glasgow University Framework), by careful control of acetic acid and water content in solvothermal syntheses in DMF. We show the syntheses are scaleable, and that the MOFs have high porosity. Their metastability is demonstrated through efforts to postsynthetically modify them by bromination of their internal alkyne units, which, in the case of the Hf analogue, results in partial delamination or degradation.

Results and discussion

During attempts to prepare nanoparticulate versions of **fcu** topology Zr(rv) MOFs^{13,40} as part of our investigations into drug delivery, ⁴¹ it was found that addition of high quantities of acetic acid and water to DMF-based solvothermal syntheses containing $ZrCl_4$ and $EDB-H_2$ resulted in formation of a new phase. This new MOF, termed GUF-12(Zr), was suspected to be the **hcp** analogue due to its characteristic hexagonal plate morphology and the nature of its powder X-ray diffractogram.

The optimal conditions to isolate the hcp phases of both the Zr(IV) and Hf(IV) congeners of GUF-12 were identified via modulated solvothermal self-assembly. Specifically, 0.34 mmol each of MCl₄ (M = Zr or Hf) and EDB-H₂ (prepared according to a modified literature protocol 13,42) were combined in 15 ml DMF, with addition of 75 µL deionised water (0.5% v/v) and 2.12 mL acetic acid (37.1 mmol, or 110 equiv. compared to the metal ion). The mixture was heated to 150 °C overnight in a PTFE-lined stainless steel autoclave, and the product isolated by centrifugation once cooled. Both the deliberate addition of water, and the use of a specific quantity of acetic acid as modulator, were key to ensure isolation of the hcp phases rather than the fcu analogue or other materials (see ESI,† Section S2). These observations tally with our previous mechanistic study that describes how the addition of large amounts of carboxylate modulator to syntheses is required to form the classical $[M_6O_4(OH)_4]$ clusters found in the fcu phases, while concomitant addition of water induces cluster merging to form the [M₁₂O₈(OH)₁₄] units that comprise the hcp phases.²² Increasing water content in syntheses containing Hf(IV) and BPDC2- has previously led to the isolation of the hns phase over the hcp analogue,30 but with the EDB2- linker only hcp phase

CrystEngComm Paper

materials were formed when water content in syntheses was increased while retaining 110 equiv. of added acetic acid. In contrast, reducing the amount of acetic acid modulator in syntheses occasionally resulted in the failure to produce a MOF.

Even with careful optimisation of the synthesis conditions, single crystals large enough for characterisation by single crystal X-ray diffraction were unable to be grown for either GUF-12 analogue. SEM analysis showed formation of micronscale hexagonal plates <100 nm in depth that are aggregated into a "desert rose" morphology, which is characteristic of MOF materials with this **hcp** topology (Fig. 2a and b).³⁰ The structure of these materials was therefore determined by a combination of powder X-ray diffraction analysis and the use of model structures derived from density functional theory (DFT) calculations. Structural models of the hcp phase were constructed from the parent fcu phase, and then geometryoptimised by DFT calculations using the CP2K code (see ESI,† Section S3). These optimised structures confirmed the kinetic stability of the hcp topology models for the Zr(IV) and Hf(IV) analogues.

Qualitative comparison of the powder X-ray diffractograms calculated from these DFT-derived hcp structures with those found experimentally (as well as those calculated from the crystal structures of the fcu phases) clearly indicate that GUF-12(Zr) and GUF-12(Hf) adopt the hcp topology (Fig. 2c).

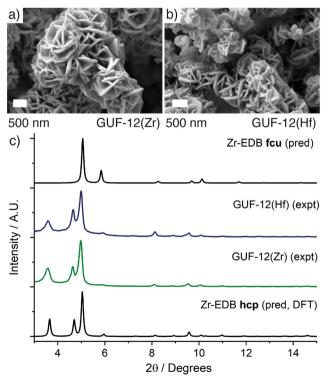


Fig. 2 Scanning electron micrographs of the desert rose morphology of a) GUF-12(Zr) and b) GUF-12(Hf). c) Stacked powder X-ray diffractograms of GUF-12(Zr) and GUF-12(Hf) compared to patterns predicted for the hcp phase, derived from DFT model structures, and for the fcu phase, derived from the single crystal structures. 13

Quantitative Pawley fitting of the diffractograms (see ESI,† Section S4) in space group P63/mmc, using the Topas Academic 6.0 software package, 43 confirmed that these phase pure, and allowed accurate materials were determination of the lattice parameters of these materials: GUF-12(Zr) a = 21.6121(31) Å, c = 48.014(12) Å; GUF-12(Hf) a = 21.5349(32) Å, c = 47.869(13) Å (Fig. 3). The DFToptimised lattice parameters were within 0.6% of the experimental parameters. We also note that GUF-12(Hf) has a slightly smaller unit cell than GUF-12(Zr), due to slightly shorter Hf-O bonds.

Bulk composition was also assessed by thermogravimetric analysis (TGA) of the GUF-12 samples after activation at 120 °C for 20 h under turbomolecular pump vacuum to remove residual solvents (Fig. 4a). The metal oxide residue remaining after heating in air to 800 °C is indicative of metal content in the pristine MOF. For both GUF-12(Zr) and GUF-12(Hf), the residues were slightly higher than would be predicted for a pristine hcp phase; 42.1% wt for GUF-12(Zr) (theoretical: 40.8% wt) and 56.8% wt for GUF-12(Hf) (theoretical: 54.1% wt). These values suggest that the fcu phase is not significantly present in either case as the hcp phase has a higher overall metal weight percentage than the analogous fcu phase (theoretical residues of 34.9% wt and 47.8% wt would be expected for the pristine Zr(IV) and Hf(IV) fcu phases, respectively). Furthermore, these TGA results suggest that the hcp phases may exhibit some missing linker defects (replacement of EDB²⁻ linkers by smaller chargecompensating acetates reduces the relative organic content in the MOF, increasing the metal weight percentage and

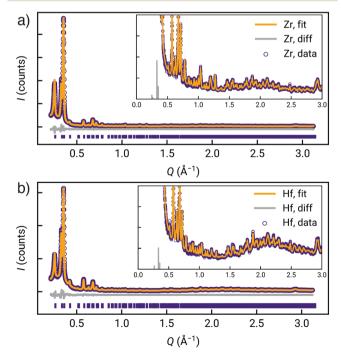


Fig. 3 Quantitative Pawley fitting (with insets to show low intensity reflections) of the powder X-ray diffractograms of a) GUF-12(Zr) and b) GUF-12(Hf).

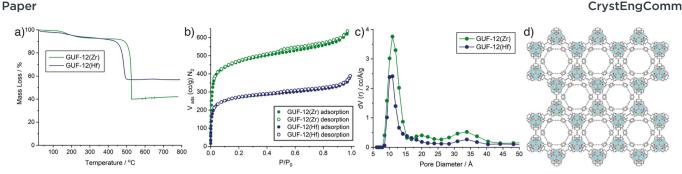


Fig. 4 a) Thermogravimetric analyses of GUF-12(Zr) and GUF-12(Hf) in air. b) N_2 adsorption desorption isotherms (77 K) of GUF-12(Zr) and GUF-12(Hf) with c) pore-size distributions (N_2 at 77 K on carbon, slit pore, QSDFT, equilibrium model) calculated from the isotherms. d) Portion of the DFT model structure of GUF-12(Zr) viewed down the crystallographic c axis to visualise the hexagonal channel 11 Å in diameter.

subsequent TGA residue).⁴¹ This is commensurate with ¹H NMR spectra of acid-digested samples (see ESI,† Section S5), which show the presence of acetate even after activation, indicating that the acetate groups are present as charge compensating defects rather than pore-bound solvents. Resonances that could be assigned to formate, produced by decomposition of DMF, were not observed in the materials.

A pristine defect-free hcp structure would have formula [M₁₂O₈(OH)₁₄(EDB)₉]. ¹H NMR spectroscopic analysis of activated, then acid-digested GUF-12(Zr) gives a 1:3.3 ratio of acetate to linker; assuming that one EDB²⁻ is replaced by two acetates gives a formula of [Zr₁₂O₈(OH)₁₄(EDB)_{7.8}(CH₃COO)_{2.4}], which would leave a theoretical 42.5% wt ZrO2 residue after thermogravimetric analysis, matching well with the observed 42.1% wt. For GUF-12(Hf), the acetate content measured by ¹H NMR spectroscopy is higher, at an approximate 1:2.5 acetate to EDB²⁻ ratio. Similar levels of defectivity have been observed elsewhere for the hcp phase prepared from Zr(IV) and BDC2- using acetic acid modulated syntheses; these defects enhance its catalytic activity.33 Taking a similar approach, a formula of [Hf₁₂O₈(OH)₁₄(EDB)_{7.5}(CH₃COO)_{3.0}] for GUF-12(Hf) would correlate with the NMR spectroscopic data and leave a theoretical HfO2 residue of 56.3% wt, close to the experimental value of 56.8% wt. This greater acetate incorporation of the Hf(IV) congener may be reflected in its lower overall thermal decomposition temperature compared to the Zr(IV) analogue, as observed by TGA (Fig. 4a). The decomposition temperatures are broadly similar to the fcu analogues.13

The reliability of the synthetic method allowed us to upscale the synthesis of the **hcp** phases to quantities suitable for porosity analysis. N_2 adsorption/desorption isotherms of GUF-12(Zr) and GUF-12(Hf) were collected at 77 K after activation of the samples at 120 °C for 20 h under vacuum (Fig. 4b). Both MOFs exhibit typical type I isotherms, associated with microporous materials, with small increases in uptake between 0.9 and 1.0 P/P_0 , indicating adsorption occurring in interparticle spacing or surface roughness. This can be explained by the aggregated "desert rose" morphology of the \sim 100 nm thick hexagonal particles, which feature multiple surfaces and crevices where nitrogen can be adsorbed. Brunauer–Emmett–Teller (BET) areas were

calculated from the experimental adsorption isotherms using BETSI, a publicly available software package that fully implements the extended Rouquerol criteria for an unambiguous BET area assignment (see ESI,† Section S6).44 The BET areas were found to be 1798 m² g⁻¹ and 1005 m² g⁻¹ for GUF-12(Zr) and GUF-12(Hf), respectively, with pore volumes of 1.03 cm³ g⁻¹ and 0.59 cm³ g⁻¹. As expected, 30,35 these are lower than those reported for the fcu analogues (3280 m² g⁻¹ and 2000 m² g⁻¹, for the Zr and Hf congeners, respectively).13 Grand Canonical Monte Carlo (GCMC) simulations were performed to assess the potential total porosity of the two MOFs (see ESI,† Section S7). Simulated N2 adsorption isotherms for both GUF-12(Zr) and GUF-12(Hf) showed higher N2 uptakes and larger predicted BET areas (2765 m² g⁻¹ and 2127 m² g⁻¹, for the Zr and Hf congeners, respectively). GCMC simulations often overpredict porosity compared to experiment, but the magnitude of the difference between the experimental and simulated N₂ uptakes suggest that the isolated MOFs may be partially amorphized or not fully activated.

In each isotherm, small type H4 hysteresis loops are discernible, which are indicative of minor levels of mesoporosity that could be a consequence of defectivity in the samples. Pore-size distributions (Fig. 4c), calculated from the experimental isotherms (N_2 on carbon at 77 K, slit pore/QSDFD equilibrium) show a significant pore around 11 Å in diameter for each MOF, which correlates closely to the hexagonal pore evident along the crystallographic c axis (Fig. 4d), and is smaller than the major pore observed in the **fcu** analogues (\sim 12.5 Å). A broad feature is observed around 34 Å for each **hcp** MOF, which may be indicative of the defectivity implied by 1 H NMR spectroscopy and TGA. This combination of high porosity and significant defectivity indicates the potential for application of the GUF-12 congeners in catalysis. 33

We and others have previously shown that MOFs linked by ligands with internal alkene^{12,45-48} and alkyne^{12,13,49,50} subunits can be postsynthetically modified by halogenation. Specifically, we have demonstrated that the Zr(IV) and Hf(IV) **fcu** phases linked by EDB²⁻ can be quantitatively brominated in a single-crystal to single-crystal manner.¹³ With two different linker environments in the **hcp** phases in this work,

CrystEngComm **Paper**

we wished to determine if (i) the linkers were accessible to bromination, and (ii) if this would result in a reactive delamination to form a nanosheet phase. Under conditions identical to those we have previously utilised for the fcu analogue, 13 it was possible to quantitatively brominate the EDB²⁻ ligands of the **hcp** materials, as assessed by ¹H and ¹³C NMR spectroscopy of acid-digested samples. However, PXRD analysis of the brominated materials showed that stability was an issue when samples were scaled up, with inconsistent results. In the case of GUF-12(Hf), additional Bragg reflections were present that may represent degradation of the MOF or delamination, underlining the metastability of the hcp MOFs (see ESI,† Section S8).

Conclusions

We have shown that, by careful consideration of synthetic conditions, it is possible to synthesise Zr(IV) and Hf(IV) MOFs of EDB²⁻ with the **hcp** topology to complement their established fcu analogues. The role of both water and acetic acid has been explored to optimise syntheses and reliably reproduce the materials on an increased scale, allowing characterisation of their porosity and possible defectivity, suggesting potential applications in heterogeneous catalysis. The hcp phases are likely kinetic products relative to the analogous fcu topology MOFs; moreover, the hcp materials are metastable, as demonstrated by partial degradation of GUF-12(Hf) during attempts to postsynthetically brominate the EDB²⁻ linkers, in contrast to the stability of the **fcu** phase under identical conditions.¹³ Nevertheless, this work shows that careful control of modulated self-assembly allows access to new MOF materials exhibiting desirable physical properties within well-established phase spaces.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

R. S. F. thanks the Royal Society for receipt of a URF and the University of Glasgow for funding. The work has been supported by the European Research Council (ERC) under the European Union's Horizon 2020 Programme for Research and Innovation (R. S. F.: grant agreement no. 677289, SCoTMOF, ERC-2015-STG; D. F. J.: grant agreement no. 726380, NanoMOFdeli, ERC-2016-COG). M. J. C. thanks the School of Chemistry at the University of Nottingham for receipt of a Hobday Fellowship. M. R. A. K. acknowledges support from the Cambridge Trust Scholarship and the Trinity-Henry Barlow Scholarship. We acknowledge the use of the ARCHER2 supercomputer through membership of the UK's HPC Materials Chemistry Consortium, which is funded by EPSRC grant no. EP/R029431. The data which underpin this submission are free to dowload at https://dx.doi.org/10.5525/ gla.researchdata.1406.

References

- 1 H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, Science, 2013, 341, 1230444.
- 2 P. Z. Moghadam, A. Li, X.-W. Liu, R. Bueno-Perez, S.-D. Wang, S. B. Wiggin, P. A. Wood and D. Fairen-Jimenez, Chem. Sci., 2020, 11, 8373-8387.
- 3 R. Freund, S. Canossa, S. M. Cohen, W. Yan, H. Deng, V. Guillerm, M. Eddaoudi, D. G. Madden, D. Fairen-Jimenez, H. Lyu, L. K. Macreadie, Z. Ji, Y. Zhang, B. Wang, F. Haase, C. Wöll, O. Zaremba, J. Andreo, S. Wuttke and C. S. Diercks, Angew. Chem., Int. Ed., 2021, 60, 23946-23974.
- 4 C. Ma, L. Zheng, G. Wang, J. Guo, L. Li, Q. He, Y. Chen and H. Zhang, Aggregate, 2022, 3, e145.
- 5 T. Devic and C. Serre, Chem. Soc. Rev., 2014, 43, 6097-6115.
- 6 R. S. Forgan, Chem. Sci., 2020, 11, 4546-4562.
- 7 D. Bara, E. Meekel, I. Pakamore, C. Wilson, S. Ling and R. S. Forgan, Mater. Horiz., 2021, 8, 3377-3386.
- 8 Y. Bai, Y. Dou, L.-H. Xie, W. Rutledge, J.-R. Li and H.-C. Zhou, Chem. Soc. Rev., 2016, 45, 2327-2367.
- 9 J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, J. Am. Chem. Soc., 2008, 130, 13850-13851.
- 10 A. Schaate, P. Roy, T. Preuße, S. J. Lohmeier, A. Godt and P. Behrens, Chem. - Eur. J., 2011, 17, 9320-9325.
- 11 J. Lippke, B. Brosent, T. von Zons, E. Virmani, S. Lilienthal, T. Preuße, M. Hülsmann, A. M. Schneider, S. Wuttke, P. Behrens and A. Godt, Inorg. Chem., 2017, 56, 748-761.
- 12 R. J. Marshall, S. L. Griffin, C. Wilson and R. S. Forgan, Chem. - Eur. J., 2016, 22, 4870-4877.
- 13 R. J. Marshall, S. L. Griffin, C. Wilson and R. S. Forgan, J. Am. Chem. Soc., 2015, 137, 9527-9530.
- 14 M. Schulz, N. Marquardt, M. Schäfer, D. P. Warwas, S. Zailskas and A. Schaate, Chem. - Eur. J., 2019, 25, 13598-13608.
- 15 X. Li, J. Xie, Z. Du, L. Jiang, G. Li, S. Ling and K. Zhu, Chem. Sci., 2022, 13, 6291-6296.
- 16 M. Perfecto-Irigaray, G. Beobide, O. Castillo, I. da Silva, D. García-Lojo, A. Luque, A. Mendia and S. Pérez-Yáñez, Chem. Commun., 2019, 55, 5954-5957.
- 17 V. Bon, I. Senkovska, M. S. Weiss and S. Kaskel, CrystEngComm, 2013, 15, 9572-9577.
- 18 M. J. Cliffe, W. Wan, X. Zou, P. A. Chater, A. K. Kleppe, M. G. Tucker, H. Wilhelm, N. P. Funnell, F.-X. Coudert and A. L. Goodwin, Nat. Commun., 2014, 5, 4176.
- 19 D. N. Johnstone, F. C. N. Firth, C. P. Grey, P. A. Midgley, M. J. Cliffe and S. M. Collins, J. Am. Chem. Soc., 2020, 142, 13081-13089.
- 20 V. Guillerm, F. Ragon, M. Dan-Hardi, T. Devic, M. Vishnuvarthan, B. Campo, A. Vimont, G. Clet, Q. Yang, G. Maurin, G. Férey, A. Vittadini, S. Gross and C. Serre, Angew. Chem., Int. Ed., 2012, 51, 9267-9271.
- 21 V. V. Butova, A. P. Budnyk, K. M. Charykov, K. S. Vetlitsyna-Novikova, C. Lamberti and A. V. Soldatov, Chem. Commun., 2019, 55, 901-904.

- 22 F. C. N. Firth, M. W. Gaultois, Y. Wu, J. M. Stratford, D. S. Keeble, C. P. Grey and M. J. Cliffe, *J. Am. Chem. Soc.*, 2021, 143, 19668–19683.
- 23 M. J. Cliffe, E. Castillo-Martínez, Y. Wu, J. Lee, A. C. Forse, F. C. N. Firth, P. Z. Moghadam, D. Fairen-Jimenez, M. W. Gaultois, J. A. Hill, O. V. Magdysyuk, B. Slater, A. L. Goodwin and C. P. Grey, J. Am. Chem. Soc., 2017, 139, 5397–5404.
- 24 A. A. Bezrukov, K. W. Törnroos, E. Le Roux and P. D. C. Dietzel, *Chem. Commun.*, 2018, 54, 2735–2738.
- 25 S. Waitschat, H. Reinsch and N. Stock, *Chem. Commun.*, 2016, 52, 12698–12701.
- 26 S. Waitschat, H. Reinsch, M. Arpacioglu and N. Stock, CrystEngComm, 2018, 20, 5108–5111.
- 27 S. Leubner, V. E. G. Bengtsson, K. Synnatschke, J. Gosch, A. Koch, H. Reinsch, H. Xu, C. Backes, X. Zou and N. Stock, J. Am. Chem. Soc., 2020, 142, 15995–16000.
- 28 M. Ermer, J. Mehler, M. Kriesten, Y. S. Avadhut, P. S. Schulz and M. Hartmann, *Dalton Trans.*, 2018, 47, 14426–14430.
- 29 L. Zhou, F. Liu, J. Wang, R. Chen and Y. Chen, *CrystEngComm*, 2021, 23, 2961–2967.
- 30 F. C. N. Firth, M. J. Cliffe, D. Vulpe, M. Aragones-Anglada, P. Z. Moghadam, D. Fairen-Jimenez, B. Slater and C. P. Grey, J. Mater. Chem. A, 2019, 7, 7459–7469.
- 31 B. Moll, T. Müller, C. Schlüsener, A. Schmitz, P. Brandt, S. Öztürk and C. Janiak, *Mater. Adv.*, 2021, 2, 804–812.
- 32 S. B. Peh, Y. Cheng, J. Zhang, Y. Wang, G. H. Chan, J. Wang and D. Zhao, *Dalton Trans.*, 2019, **48**, 7069–7073.
- 33 X. Chen, Y. Lyu, Z. Wang, X. Qiao, B. C. Gates and D. Yang, ACS Catal., 2020, 10, 2906–2914.
- 34 R. Dai, F. Peng, P. Ji, K. Lu, C. Wang, J. Sun and W. Lin, *Inorg. Chem.*, 2017, 56, 8128–8134.
- 35 P. Ji, K. Manna, Z. Lin, X. Feng, A. Urban, Y. Song and W. Lin, *J. Am. Chem. Soc.*, 2017, **139**, 7004–7011.
- 36 M. R. Momeni and C. J. Cramer, *Chem. Mater.*, 2018, **30**, 4432–4439.
- 37 Y.-Y. Zhu, G. Lan, Y. Fan, S. S. Veroneau, Y. Song, D. Micheroni and W. Lin, *Angew. Chem., Int. Ed.*, 2018, 57, 14090–14094.
- 38 K. Lu, C. He, N. Guo, C. Chan, K. Ni, G. Lan, H. Tang, C. Pelizzari, Y. X. Fu, M. T. Spiotto, R. R. Weichselbaum and W. Lin, *Nat. Biomed. Eng.*, 2018, 2, 600–610.
- 39 L. Zhou, S. Wang, Y. Chen and C. Serre, *Microporous Mesoporous Mater.*, 2019, 290, 109674.
- 40 X.-L. Lv, M. Tong, H. Huang, B. Wang, L. Gan, Q. Yang, C. Zhong and J.-R. Li, *J. Solid State Chem.*, 2015, 223, 104–108.

- 41 I. Abánades Lázaro and R. S. Forgan, Coord. Chem. Rev., 2019, 380, 230–259.
- 42 T. Gadzikwa, B.-S. Zeng, J. T. Hupp and S. T. Nguyen, *Chem. Commun.*, 2008, 3672–3674.
- 43 A. A. Coelho, J. Evans, I. Evans, A. Kern and S. Parsons, *Powder Diffr.*, 2011, **26**, S22–S25.
- 44 J. W. M. Osterrieth, J. Rampersad, D. Madden, N. Rampal, L. Skoric, B. Connolly, M. D. Allendorf, V. Stavila, J. L. Snider, R. Ameloot, J. Marreiros, C. Ania, D. Azevedo, E. Vilarrasa-Garcia, B. F. Santos, X.-H. Bu, Z. Chang, H. Bunzen, N. R. Champness, S. L. Griffin, B. Chen, R.-B. Lin, B. Coasne, S. Cohen, J. C. Moreton, Y. J. Colón, L. Chen, R. Clowes, F.-X. Coudert, Y. Cui, B. Hou, D. M. D'Alessandro, P. W. Doheny, M. Dincă, C. Sun, C. Doonan, M. T. Huxley, J. D. Evans, P. Falcaro, R. Ricco, O. Farha, K. B. Idrees, T. Islamoglu, P. Feng, H. Yang, R. S. Forgan, D. Bara, S. Furukawa, E. Sanchez, J. Gascon, S. Telalović, S. K. Ghosh, S. Mukherjee, M. R. Hill, M. M. Sadiq, P. Horcajada, P. Salcedo-Abraira, K. Kaneko, R. Kukobat, J. Kenvin, S. Keskin, S. Kitagawa, K.-I. Otake, R. P. Lively, S. J. A. DeWitt, P. Llewellyn, B. V. Lotsch, S. T. Emmerling, A. M. Pütz, C. Martí-Gastaldo, N. M. Padial, J. García-Martínez, N. Linares, D. Maspoch, J. A. Suárez del Pino, P. Moghadam, R. Oktavian, R. E. Morris, P. S. Wheatley, J. Navarro, C. Petit, D. Danaci, M. J. Rosseinsky, A. P. Katsoulidis, M. Schröder, X. Han, S. Yang, C. Serre, G. Mouchaham, D. S. Sholl, R. Thyagarajan, D. Siderius, R. Q. Snurr, R. B. Goncalves, S. Telfer, S. J. Lee, V. P. Ting, J. L. Rowlandson, T. Uemura, T. Iiyuka, M. A. van der Veen, D. Rega, V. Van Speybroeck, S. M. J. Rogge, A. Lamaire, K. S. Walton, L. W. Bingel, S. Wuttke, J. Andreo, O. Yaghi, B. Zhang, C. T. Yavuz, T. S. Nguyen, F. Zamora, C. Montoro, H. Zhou, A. Kirchon and D. Fairen-Jimenez, Adv. Mater., 2022, 34, 2201502.
- 45 C. A. Walshe, A. J. R. Thom, C. Wilson, S. Ling and R. S. Forgan, *Chem. Eur. J.*, 2022, **28**, e202201364.
- 46 R. J. Marshall, T. Richards, C. L. Hobday, C. F. Murphie, C. Wilson, S. A. Moggach, T. D. Bennett and R. S. Forgan, *Dalton Trans.*, 2016, 45, 4132–4135.
- 47 S. C. Jones and C. A. Bauer, *J. Am. Chem. Soc.*, 2009, **131**, 12516–12517.
- 48 T. J. Azbell, R. M. Mandel, J.-H. Lee and P. J. Milner, ACS Appl. Mater. Interfaces, 2022, 14, 53928–53935.
- 49 D. Frahm, F. Hoffmann and M. Fröba, *Cryst. Growth Des.*, 2014, 14, 1719–1725.
- 50 T. J. Matemb Ma Ntep, H. Reinsch, J. Liang and C. Janiak, Dalton Trans., 2019, 48, 15849–15855.