



Cite this: DOI: 10.1039/d4sc03242j

All publication charges for this article have been paid for by the Royal Society of Chemistry

Unleashing the potential of Li–O₂ batteries with electronic modulation and lattice strain in pre-lithiated electrocatalysts†

Zhengcai Zhang,[‡]^a Dulin Huang,[‡]^a Shuochao Xing,^a Minghui Li,^a Jing Wu,^a Zhang Zhang,^a Yaying Dou^{*ab} and Zhen Zhou^{ib}^{*a}

Efficient catalysts are indispensable for overcoming the sluggish reaction kinetics and high overpotentials inherent in Li–O₂ batteries. However, the lack of precise control over catalyst structures at the atomic level and limited understanding of the underlying catalytic mechanisms pose significant challenges to advancing catalyst technology. In this study, we propose the concept of precisely controlled pre-lithiated electrocatalysts, drawing inspiration from lithium electrochemistry. Our results demonstrate that Li⁺ intercalation induces lattice strain in RuO₂ and modulates its electronic structure. These modifications promote electron transfer between catalysts and reaction intermediates, optimizing the adsorption behavior of Li–O intermediates. As a result, Li–O₂ batteries employing Li_{0.52}RuO₂ exhibit ultrahigh energy efficiency, long lifespan, high discharge capacity, and excellent rate performance. This research offers valuable insights for the design and optimization of efficient electrocatalysts at the atomic level, paving the way for further advancements in Li–O₂ battery technology.

Received 17th May 2024
Accepted 20th July 2024

DOI: 10.1039/d4sc03242j

rsc.li/chemical-science

Introduction

Lithium–oxygen (Li–O₂) batteries have garnered significant attention as a promising “beyond lithium-ion battery” technology for next-generation energy storage systems. By capitalizing on the lightweight properties of lithium metal and the abundant availability of atmospheric oxygen, Li–O₂ batteries offer an exceptional theoretical energy density of up to 5220 W h kg^{−1}.^{1–3} This, in conjunction with their cost-effectiveness and low pollution characteristics, positions Li–O₂ batteries as an enticing solution in the realm of electrochemical energy storage. Nevertheless, the practical implementation encounters many hurdles primarily arising from the insulating nature of Li₂O₂, resulting in diminished energy efficiency, rapid capacity decay, and sluggish reaction kinetics.^{4–6}

Addressing these challenges, extensive research efforts have been directed towards both solid and liquid catalysts. However, the utilization of liquid catalysts often introduces the issue of

the “shuttle effect”, resulting in the corrosion of lithium metal and subsequent reduction in battery durability.⁷ Alternatively, various solid catalysts, including metal oxides,^{8,9} alloys,⁵ and high-entropy catalysts,¹⁰ have been extensively investigated in Li–O₂ batteries. Previous studies emphasized the importance of modulating the adsorption strength between LiO₂ and catalyst surfaces to facilitate the formation and decomposition of Li₂O₂, a pivotal process in Li–O₂ batteries.^{10–13}

To further enhance the catalytic activity of these candidates, surface engineering techniques are commonly employed to modulate atom arrangement and electronic structure. Established methods such as crystal facet engineering, defect engineering, and surface/interface modification are widely utilized towards achieving these objectives.^{14–17} Among these strategies, doping with heteroatoms has shown promising electrocatalytic activity for boosting the performance of Li–O₂ batteries. By introducing heteroatoms with varying valence states and electronegativity, the charge and spin density of materials can be redistributed, thereby influencing the adsorption of oxygen-containing intermediates at active sites.

For instance, research conducted by Lu *et al.* demonstrated that incorporating excess Co into the (101) plane of RuO₂ results in abundant Ru/Co dual-atom sites on the RuO₂ (110) surface. This approach effectively optimizes both charge transfer and the accessibility of the intermediate *OOH species in zinc–air batteries.¹⁸ However, traditional doping methods often entail complex preparation procedures, impeding precise control over the foreign element concentration and the rational design of

^aInterdisciplinary Research Center for Sustainable Energy Science and Engineering (IRC4SE²), School of Chemical Engineering, Zhengzhou University, Zhengzhou 450001, China. E-mail: yydou@zzu.edu.cn; zhenzhou@zzu.edu.cn

^bKey Laboratory of Advanced Energy Materials Chemistry (Ministry of Education), College of Chemistry, Nankai University, Tianjin 300071, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4sc03242j>

‡ Zhengcai Zhang and Dulin Huang contributed equally to this work.



catalysts. Moreover, the structure–activity relationship of catalysts prepared *via* traditional chemical methods, especially at the atomic level, remains elusive for oxygen electrochemical processes in Li–O₂ batteries.

Therefore, it is imperative to develop an efficient and controllable preparation method that strikes a delicate balance between cost-effectiveness and the precise preparation of catalysts. This will provide a solid foundation for the development of high-performance Li–O₂ batteries.

Electron-ion coupled transfer in electrochemistry offers a promising alternative for modifying the electronic or crystal structure of host materials. Unlike conventional chemical synthesis, electrochemical techniques operate at lower temperatures and pressures, leading to reduced energy consumption and waste generation. Furthermore, these methods afford greater control over impurity concentration through adjustable electrochemical parameters.^{19–21} This controllability allows for increased freedom in modulating the atom arrangement and electronic properties of catalytic materials, thereby facilitating the design and synthesis of tailored catalysts.

Electrochemical methods, including galvanic replacement, electrochemical exfoliation, and electrochemical insertion/extraction, have found wide application in the synthesis of energy catalytic materials, demonstrating promising outcomes in various electrocatalytic applications such as water splitting and carbon dioxide reduction.^{22–24} For example, the electrochemical treatment of Li₂Co₂O₄ spinel facilitates the formation of amorphous active layers, thereby enhancing the oxygen evolution reaction (OER) due to the presence of Co⁴⁺ ions and oxygen sites with electronic holes.²⁵ Similarly, treating MnO₂ with lithium exhibited improved catalytic performance in Li–O₂ batteries, indicating the promising recycling of depleted Li–MnO₂ batteries.²⁶ Although these examples underscore the distinct advantages of electrochemical treatments in fabricating efficient catalysts, the specific catalytic mechanisms still need to be further revealed, especially in Li–O₂ batteries.

Drawing inspiration from this perspective, we propose a simple lithium electrochemical tuning method to enhance the catalytic activity of RuO₂, the most commonly used representative in Li–O₂ batteries. This method allows for the quantitative adjustment of Li⁺ concentration (*x*). The findings reveal that Li⁺ not only induces lattice strain by embedding into the lattice interstitial of RuO₂ but also functions as an electron donor, directly modulating the electronic structure of RuO₂. Specifically, the valence state of Ru decreases with Li⁺ intercalation, accompanied by the formation of oxygen vacancies. These modifications facilitate efficient electron transfer from the catalyst to the reaction intermediates while optimizing the adsorption behavior of the Li–O intermediates, particularly LiO₂, on the electrode surface. Consequently, Li–O₂ batteries employing Li_{0.52}RuO₂ as a catalyst demonstrate ultrahigh energy conversion efficiency and long-term reversibility. The elucidation of the atomic-level catalytic mechanism provides valuable insights into the rational design and optimization of advanced electrocatalysts for Li–O₂ batteries.

Experimental

Fabrication of Li_{*x*}RuO₂ cathodes

Firstly, RuO₂@CNT (carbon nanotubes) was prepared using the method described previously.⁸ Then, a mixture comprising 90 wt% of RuO₂@CNT and 10 wt% polyvinylidene difluoride (PVDF) binder was prepared by mixing them with *N*-methylpyrrolidone (NMP) in a mortar. After ultrasonic dispersion, the mixture was evenly spread onto a carbon paper with a diameter of 12 mm. Subsequently, the resulting cathode was dried at 110 °C under vacuum for 12 hours before use.

To prepare Li_{*x*}RuO₂, a Li⁺ intercalation process was employed. Specifically, the RuO₂@CNT cathode was assembled into CR2032 coin cells, with Li foil as the counter-electrode. The electrolyte was a 1 M bis(trifluoromethane)sulfonamide lithium salt (LiTFSI) dissolved in tetraethylene glycol dimethyl ether (TEGDME). The Li⁺ intercalation into RuO₂ was achieved by discharging the cell at a constant current density of 10 mA g^{−1} in an argon atmosphere. While the amount of Li⁺ intercalation was controlled by the discharge time. The obtained Li_{*x*}RuO₂ was used as the as-prepared cathode for Li–O₂ batteries.

Battery assembly and tests

The Li–O₂ batteries were assembled inside an Ar-filled glovebox, in which the as-prepared electrode, Li foil and glass fiber paper (Whatman, GF/D) were used as the cathode, anode and separator, respectively. 100 μL of electrolyte (1 M LiTFSI/TEGDME) was added to the battery. Before electrochemical tests, the batteries were purged with 99.995% O₂ for 1 h. Galvanostatic discharge–charge tests were conducted under a LAND CT2001A battery testing system. The current and specific capacity were calculated based on the active mass of the cathode. Linear sweep voltammetry (LSV) curves were conducted with an electrochemical workstation (Solartron 1470E).

Experimental characterization

After discharge/charge tests, the batteries were disassembled in a glovebox. The cathode was then removed and washed with anhydrous acetonitrile solvent, followed by vacuum drying before undergoing a series of characterizations. X-ray diffraction (XRD) analysis was performed using an Ultima IV X-ray diffractometer equipped with a graphite monochromatized Cu–Kα radiation source, operating at 40 kV and 40 mA. The morphology of the samples was examined using a Hitachi S4800 field emission scanning electron microscope (FESEM), while the crystal structure was analyzed using a JEM-2800 transmission electron microscope (TEM). Surface elemental properties were analyzed by X-ray photoelectron spectroscopy (XPS) using a Thermo Scientific K-Alpha+ instrument. All spectra were calibrated using the C 1s peak at 284.8 eV.

Differential electrochemical mass spectrometry (DEMS) measurements of Li–O₂ batteries. Quantitative DEMS was employed to investigate the stability and reversibility of Li–O₂ batteries. A custom-designed Li–O₂ battery, equipped with two securely attached poly(ether-ether-ketone) (PEEK) capillary tubes for gas inlet and outlet, was connected to a commercially



available magnetic sector mass spectrometer (Thermo Fisher) using a specially engineered gas purging system. The flow rate of the purging gas was precisely regulated by a digital mass flow meter (Bronkhorst). During discharging, a gas mixture of Ar/O₂ (mass ratio of 1 : 4) with a controlled flux of 0.4 sccm served as the carrier gas to accurately measure the consumption of O₂. For charging Li–O₂ batteries, high-purity (99.999%) Ar was utilized as the carrier gas to quantify O₂ evolution. The DEMS battery assembly and testing followed procedures similar to those outlined in the section on electrochemical measurements.

Computational methods

All the computations were carried out by the DFT method including van der Waals (vdW) corrections, as implemented in the Vienna *Ab Initio* Simulation Package (VASP).²⁷ The Perdew–Burke–Ernzerhof (PBE) functional within the generalized gradient approximation (GGA) was used to describe the exchange–correlation interaction.²⁸ Projector augmented wave (PAW) methods are used for pseudopotentials.²⁹ An energy cutoff of 400 eV is adopted for the plane-wave basis. The vacuum layers are set to ~30 Å to decouple the interaction between periodic images. The Brillouin zones are sampled using Gamma-centered *k*-mesh of 3 × 3 × 1. The energy convergence criterion of geometry relaxation is set to 10^{−5} eV. The rest atomic layers and adsorbates are free to relax until the net force per atom is less than 0.05 eV Å^{−1}. The DFT-D3 method is used to describe the van der Waals interaction.³⁰ The VASPKIT code is used for the post-processing of the VASP computational data.³¹ The structures were visualized using the VESTA package.³²

The differential charge density is calculated according to $\Delta\rho = \rho_{AB} - \rho_A - \rho_B$, where ρ_{AB} , ρ_A , and ρ_B represent the charge densities of Li_{*x*}RuO₂ (*x* = 0, 0.5) covered by Li₂O₂ with or without adsorbed LiO₂, and isolated LiO₂, respectively. Yellow and blue colors indicate the charge accumulation and depletion, respectively.

The adsorption energy is calculated according to the equation $E_{\text{ads}} = E_{\text{AB}} - E_{\text{A}} - E_{\text{B}}$, where E_{AB} is the total energy of Li_{*x*}O_{*y*} (*x* = 1, 2, 4, *y* = 2, 4) molecules adsorbed on the Li_{*x*}RuO₂ (*x* = 0, 0.5), E_{A} is the energy of isolated Li_{*x*}O_{*y*} (*x* = 1, 2, 4, *y* = 2, 4) molecule, E_{B} is the energy of Li_{*x*}RuO₂ substrate.

Results and discussion

Catalyst characterization

The Li⁺-intercalated RuO₂ (Li_{*x*}RuO₂) with adjustable Li⁺ concentration was prepared *via* an electrochemical lithiation process involving coupled ion–electron transfer. Linear sweep voltammetry (LSV) was conducted to investigate the Li⁺ intercalation process (Fig. S1a†). Notably, a distinct reduction peak at approximately 2 V was observed, indicating the Li⁺ intercalation into RuO₂, followed by the transformation of Li_{*x*}RuO₂ to Ru/Li₂O,^{33,34} as illustrated in Fig. 1a. Furthermore, a constant-current discharge was conducted to verify this phenomenon (Fig. S1b†). Remarkably, a prominent discharge plateau was observed around 2 V, followed by a gradual voltage decrease towards 1 V, consistent with the LSV results. These findings confirm the feasibility of synthesizing Li_{*x*}RuO₂ *via* the electrochemical approach. The precise control of Li⁺ content (*x*) in Li_{*x*}RuO₂ is of utmost importance as it allows for the accurate adjustment of the atomic structure and electronic properties of the catalyst. By constant current density discharge, a linear relationship between the Li⁺ concentration and time is established. Further details regarding the estimation of the nominal lithium concentration can be found in Fig. S2.†

XRD was conducted to investigate the influence of Li⁺ intercalation on the crystal structure of RuO₂. Fig. S3† illustrates the XRD patterns of pristine RuO₂, displaying three distinct diffraction peaks at approximately 28.1°, 35.1°, and 54.4°, in accordance with the characteristic diffraction pattern of rutile RuO₂. The analysis of Li_{*x*}RuO₂ primarily focused on the peaks at 35.1° and 54.4°, to circumvent the diffraction interference of carbon at 28.1°. Evidently, Li_{*x*}RuO₂ retain the overall diffraction characteristics of RuO₂. However, as the Li⁺ concentration increases, these peaks' positions gradually shift slightly towards lower angles, indicating expansion of the RuO₂ lattice due to Li⁺ intercalation (Fig. 1b). The simulations, as depicted in Fig. S4,† further confirm this phenomenon. The lithium intercalation levels used were 0.08, 0.25, 0.33, and 0.5, based on experimental data and computational feasibility. The calculations illustrate that Li⁺ intercalates into the octahedral interstice formed by six adjacent O atoms, rather than replacing the Ru cations, thus leading to the expansion of the RuO₂ lattice

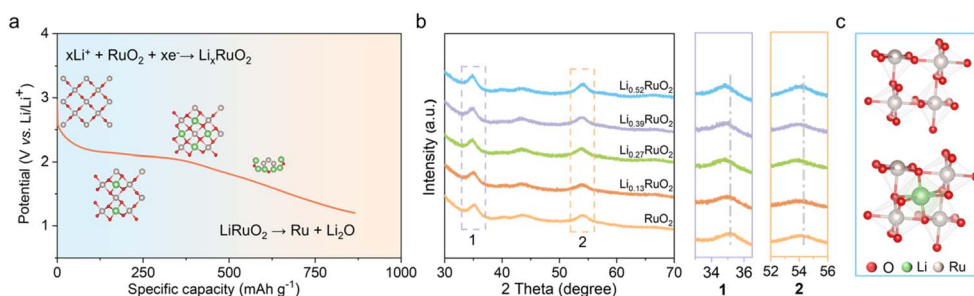


Fig. 1 (a) Schematic diagram illustrating Li⁺ intercalation into RuO₂ under a constant current density of 10 mA g^{−1}. (b) XRD patterns of Li_{*x*}RuO₂ with Li⁺ concentration *x* from 0 to 0.52 and the corresponding zoom-in images. (c) RuO₆ octahedron before (up) and after (down) Li⁺ intercalation.



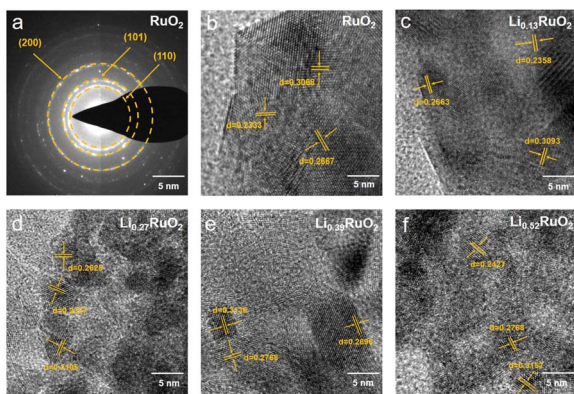


Fig. 2 The SAED patterns (a) of pristine RuO₂ and HRTEM images (b–f) of the RuO₂ with different Li⁺ concentrations.

(Fig. 1c). The fitted lattice parameters of RuO₂ before and after Li⁺ intercalation, along with the corresponding dilatation strains, are presented in Table S1.† Specifically, with increasing the lithiation degree, the expansion strains along *a*, *b*, and *c*-axis increase by 3.73%, 3.89%, and 0.26%, respectively.

The morphology and crystal structure of the thus prepared samples were analyzed using SEM and TEM. As shown in Fig. S5,† the initial cathode exhibited a uniform distribution of RuO₂ and CNT. After 16 h electrochemical treatment, no significant changes were observed, except for a slight reduction in pore size. Selected area electron diffraction (SAED) analyses shown in Fig. 2a reveal a series of lattice fringes in pristine RuO₂, corresponding to the (110), (101), and (200) planes of the rutile RuO₂. With Li⁺ intercalation, the lattice spacing gradually increases, as demonstrated in Fig. 2b–f. Specifically, in the case of Li_{0.52}RuO₂, the lattice spacings of the (110), (101), and (200) planes increase to 0.2427 nm, 0.2768 nm, and 0.3157 nm, respectively. This indicates that Li⁺ intercalation causes lattice

expansion, aligning with the observed shift of characteristic peak positions towards lower angles in XRD.

To investigate the influence of electrochemical treatment on surface chemical states and electronic structure of Li_{*x*}RuO₂, XPS was employed. Fig. 3a illustrates the Ru 3d spectra of pristine RuO₂ and a series of Li_{*x*}RuO₂ samples. The Ru 3d_{5/2} spectrum exhibits peaks at 281 and 282 eV, corresponding to Ru(III) and Ru(IV), respectively. Two satellite peaks associated with Ru 3d_{3/2} are also observed. Pristine RuO₂ exclusively displays the Ru(IV) peak at 282 eV, consistent with previous reports.^{35,36} However, upon Li⁺ intercalation, a characteristic peak of Ru(III) at 281 eV emerges. The content of Ru(IV) and Ru(III) in Li_{*x*}RuO₂ samples is summarized in Fig. 3c. With increasing Li⁺ concentration, the proportion of Ru(IV) decreases to 93.5%, 87.3%, 76.2%, and 71.4%. Moreover, both the Ru(IV) and Ru(III) peaks exhibit a slight shift towards higher binding energies, indicating electron transfer and a decrease in electron density around the Ru sites. Furthermore, an analysis of O 1s spectra was conducted, as presented in Fig. 3b. The peak around 529.4 eV in RuO₂, attributed to lattice oxygen, gradually shifts to lower binding energies with Li⁺ intercalation. This shift suggests an increased electron density surrounding the oxygen sites, indicating partial electron transfer from the Ru sites to the O sites facilitated by Li⁺ intercalation.^{37,38} Notably, after 8 h intercalation, a new peak appears around 530.5 eV, corresponding to oxygen vacancy, whose proportion gradually increases with prolonged intercalation time, as statistically demonstrated in Fig. 3d. This increase might provide additional active sites for oxygen electrochemical reactions.

Li–O₂ battery performance

A series of electrochemical tests were conducted to evaluate the unique electrocatalytic capability of the elaborately designed Li_{*x*}RuO₂ catalyst for Li–O₂ batteries. The discharge profiles at different current densities reveal that the electrochemically treated Li_{*x*}RuO₂ exhibits enhanced discharge capacity compared with pristine RuO₂ (Fig. 4a and b). Moreover, with an increase in Li⁺ intercalation, the capacity demonstrates corresponding enhancement. This can be attributed to the enhanced adsorption of intermediate LiO₂ on Li_{*x*}RuO₂, resulting in full utilization of inner space, which will be discussed in detail below.

Fig. 4c shows the first-cycle charge–discharge curve of Li–O₂ batteries with RuO₂ or Li_{*x*}RuO₂ cathode, which is another crucial criterion for evaluating the catalytic activity of materials. Compared with the RuO₂ cathode, Li–O₂ batteries based on Li_{*x*}RuO₂ demonstrated smaller charge overpotentials, which is negatively correlated with the Li⁺ concentration. That is, the higher the Li⁺ intercalation level, the lower the reaction overpotential. Notably, the first charge voltage of Li_{0.52}RuO₂-based Li–O₂ batteries decreased to approximately 3.41 V, which could effectively mitigate parasitic reactions at higher voltages. Moreover, Li–O₂ batteries based on RuO₂ displayed a limited cycle life of 150 cycles, while the batteries incorporating Li_{*x*}RuO₂ demonstrated significantly improved cycling performance (Fig. 4d). Among them, the Li–O₂ batteries utilizing Li_{0.52}RuO₂

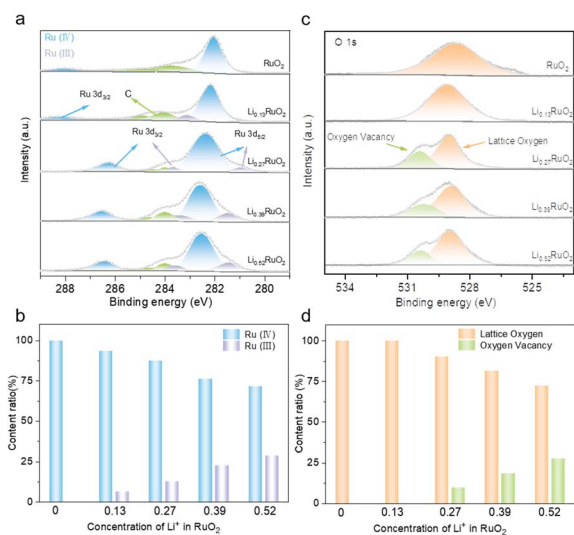


Fig. 3 XPS of Ru 3d (a) and O 1s (b) of RuO₂ and Li_{*x*}RuO₂, and (c and d) content comparison of different chemical species calculated from the fitted XPS spectra.



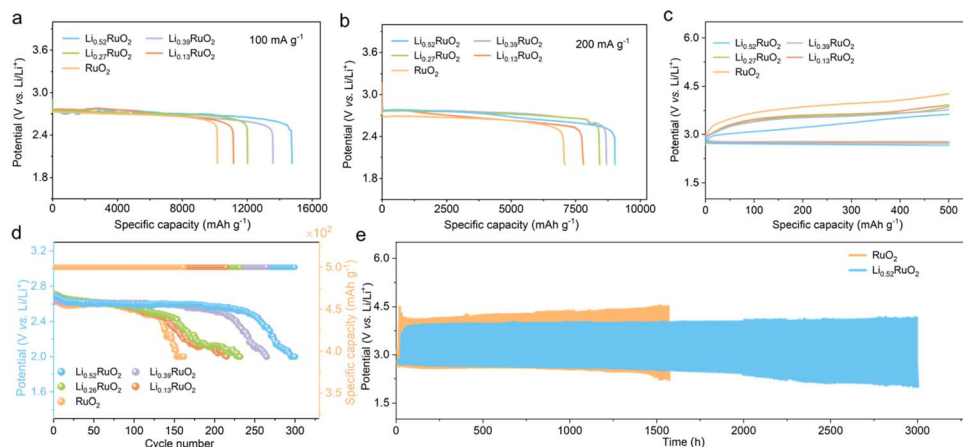


Fig. 4 Discharge profiles of Li–O₂ batteries with RuO₂ or Li_xRuO₂ cathode at a current density of (a) 100 mA g⁻¹ and (b) 200 mA g⁻¹. The first-cycle charge–discharge curve (c), terminal discharge voltages and corresponding capacity (d) and cycling stability (e) of Li–O₂ batteries with RuO₂ or Li_xRuO₂ cathode at 100 mA g⁻¹ with a limited capacity of 500 mA h g⁻¹.

exhibited the best cycling stability, with a remarkable cycle life of 300 cycles and stable operation exceeding 3000 hours (Fig. 4e). These results indicate that the Li⁺ intercalation significantly enhances the catalytic activity of Li_xRuO₂ towards Li₂O₂ decomposition, which can be attributed to additional vacancy oxygen and the modulated electronic structure, providing additional active sites and enhancing reaction kinetics.

The practical feasibility of Li_{0.52}RuO₂-based Li–O₂ batteries was evaluated at an increased current density of 500 mA g⁻¹.

Fig. 5a and b illustrate that the Li–O₂ batteries with Li_{0.52}RuO₂ demonstrated improved cycling life of 321 cycles, surpassing that with untreated RuO₂. Even at a higher cutoff capacity of 1000 mA h g⁻¹, as displayed in Fig. 5c, Li–O₂ batteries with Li_{0.52}RuO₂ demonstrated remarkable cycling stability for 153 cycles, whereas those with RuO₂ showed limited cycle life of 111 cycles due to rapid voltage increase (Fig. 5d). These results highlight the exceptional ability of Li_xRuO₂ to mitigate charging voltage and enhance cycling stability, demonstrating its practical potential. The rate performance of Li–O₂ batteries utilizing Li_{0.52}RuO₂ is depicted in Fig. 5k. In comparison with pristine RuO₂, the Li_{0.52}RuO₂-incorporating battery exhibits minimal discharge and charge voltage fluctuation, even under a high current density of 1000 mA g⁻¹, which can be attributed to enhanced kinetics of oxygen electrochemical reactions. These findings underscore the paramount significance of modulating the atom structure and electronic feature of the catalyst in enhancing the performance of Li–O₂ batteries.

To gain deeper insights into the underlying catalytic mechanism of Li_xRuO₂, which is closely linked to the component and morphology of Li–O₂ battery products and their electrochemical performance, XRD and SEM were employed to examine the cathodes in different discharge/charge states. As demonstrated in Fig. S6,† both the discharged RuO₂ and Li_xRuO₂ cathodes exhibited diffraction peaks at 32.9° and 35.0°, corresponding to the (100) and (101) crystal planes of Li₂O₂ (PDF#09-0355), indicating Li₂O₂ as the primary discharge product. Upon charging completion, the Li₂O₂ diffraction peak vanished, while the cathode peak reappeared, suggesting complete decomposition of discharge products for both RuO₂ and Li_xRuO₂ cathodes. Considering that XRD analysis provides information solely on the crystalline components, it is crucial to employ quantitative techniques like DEMS to evaluate the reversibility of Li–O₂ batteries.³⁹ The amount of O₂ consumption/evolution during battery operation can be monitored using DEMS, which is imperative for the assessment of truly rechargeable Li–O₂ batteries.

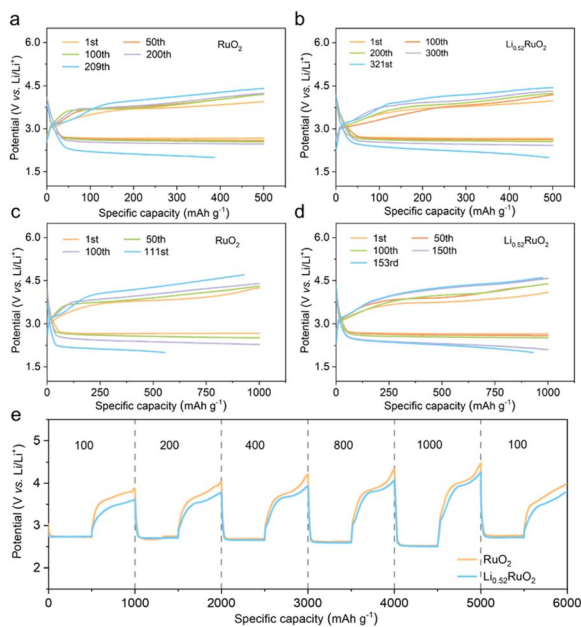


Fig. 5 Cycling performance of RuO₂ and Li_{0.52}RuO₂ in Li–O₂ batteries with a cutoff capacity of (a and b) 500 mA h g⁻¹ or (c and d) 1000 mA h g⁻¹ at a current density of 500 mA g⁻¹. (e) Rate performance of RuO₂ and Li_{0.52}RuO₂ under current density changing from 100 to 1000 mA g⁻¹.



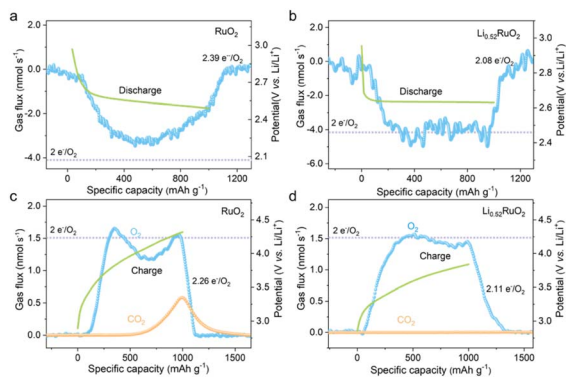


Fig. 6 DEMS analyses of gas consumption (a and b) and evolution (c and d) during discharge/charge of Li–O₂ batteries based on (a and c) RuO₂ and (b and d) Li_{0.52}RuO₂ cathodes.

For an ideally reversible Li–O₂ battery, the ratio of electrons to O₂ molecule (e^-/O_2) shall be 2.0, and O₂ is the only gaseous species involved in the discharge/recharge cycle. The typical galvanostatic discharge/charge profiles and the corresponding gas consumption/evolution rate are shown in Fig. 6. For the RuO₂ based Li–O₂ battery (Fig. 6a), a significantly deviated value of 2.39 e^-/O_2 was obtained upon discharge, with an ORR efficiency of only 80.5%, suggesting much undesired parasitic reaction. However, the e^-/O_2 ratio was quantified to be 2.08 ($\approx 2.0 e^-/O_2$) for the Li_{0.52}RuO₂-based Li–O₂ battery, as depicted in Fig. 6b, with a slight deviation of 4% from the theoretical value. This negligible discrepancy could be attributed to the inevitable shuttle effect of oxygen and Li–O intermediates. The results indicate that the discharge reaction, catalyzed by Li_{0.52}RuO₂, primarily involved Li₂O₂ formation, which is consistent with the XRD result. Furthermore, the catalytic activity of Li_{0.52}RuO₂ and RuO₂ during recharge was also evaluated using DEMS. As exhibited in Fig. 6c, the RuO₂ based Li–O₂ battery displays a high charge potential and a widely observed OER profile with a dip in the middle of charge, which usually is accompanied by a hydrogen evolution reaction (HER) resulted from the ¹O₂ attack, mirroring the missing O₂ in the OER profile.⁴⁰ Additionally, a significant amount of CO₂ was observed when the charging voltage reached approximately 4.0 V. Actually, the appearance of gaseous CO₂ during recharge is an indicator that the Li–O₂ batteries are not ideally reversible, and the amount of CO₂ generated directly reflects the extent of undesired parasitic reactions, which has been suggested to originate from the decomposition of carbon cathodes or electrolytes. On the contrary, the battery charged with Li_{0.52}RuO₂ (Fig. 6d) does not display a dip in its OER profile, which demonstrated a continuous, stable release of O₂, with negligible CO₂ generation. As a result, the ratio of charge passed to O₂ evolved with Li_{0.52}RuO₂ cathode was quantified to be 2.11, which is much lower than 2.26 of the RuO₂-based Li–O₂ battery. Based on these findings, the disappearance of these three features (OER dip, CO₂ release and ratio of e^-/O_2), the Li_{0.52}RuO₂ further confirms its superior catalytic activity. Besides, the parasitic products also were investigated through XPS. After the first cycle, the RuO₂ cathode exhibited

undecomposed Li₂O₂ and significant amounts of Li₂CO₃ byproducts (Fig. S7a†), likely due to elevated charging voltage. These byproducts, due to their wide band gap, are difficult to decompose during cycling, leading to increased charging voltage and eventual cathode passivation. As shown in Fig. S7b,† more Li₂CO₃ accumulated in the RuO₂ cathode surface after the 10th cycle. In contrast, pre-lithiated cathodes exhibited significantly lower Li₂CO₃ levels after cycling. The Li₂CO₃ content decreased progressively with increasing Li⁺ concentration. Notably, the Li_{0.52}RuO₂ cathode showed almost no Li₂CO₃ byproducts, consistent with DEMS results. Even after the 10th cycle, no significant Li₂CO₃ was observed, indicating the system's exceptional capability in suppressing side reactions. Therefore, the incorporation of Li_{0.52}RuO₂ in Li–O₂ batteries not only improves reaction kinetics but also reduces charging voltage, leading to reduced side reactions and enhanced reversibility, thereby improving the overall cycle stability.

SEM was conducted to investigate the morphological features of discharge products. As depicted in Fig. S4a,† the pristine RuO₂ electrode exhibited a homogeneous mixture of RuO₂ particles and CNTs. Upon discharge, the electrode was covered by a dense film-like discharge product (Fig. S8a†), which may be the potential reason for limited discharge capacity. However, in addition to the dense film-like discharge product, Li_xRuO₂ also exhibited some rod-like products, as presented in Fig. S8b–e.† Furthermore, increasing Li⁺ concentration promoted the growth of these products, corresponding to higher discharge capacity. This result is closely linked to the adsorption behavior of reaction intermediates on the catalyst surface, which is modulated by the electronic structure resulting from Li⁺ intercalation. It may optimize the adsorption strength of Li_xRuO₂ cathodes toward the superoxide intermediates, promoting different oxygen reduction reaction (ORR) routes. Notably, the Li_{0.52}RuO₂ cathode exhibited the highest discharge product yield and capacity. Upon charging, residual discharge products were observed on RuO₂ cathodes (Fig. S8f†), which severely reduce the availability of active sites and impede electron transfer. Conversely, the Li_xRuO₂ cathode displayed complete products decomposition, showcasing excellent reversibility (Fig. S8g–k†). These results emphasize the importance of electrochemically modulating the electronic structure of materials, optimizing the adsorption characteristics of catalysts towards intermediate species in Li–O₂ batteries. Further detailed explanations will be provided in DFT calculations sections.

Catalytic mechanism of Li_xRuO₂ catalyst

DFT calculations were employed to investigate the catalytic mechanisms of pre-lithiation RuO₂ in Li–O₂ batteries. The calculations focused on the (110) planes of RuO₂ and Li_xRuO₂, which were predominantly observed in HRTEM images. The work function (Φ), a crucial descriptor of the electron-donating capability of a solid electrocatalyst, was depicted in Fig. S9a–e.† As the Li⁺ concentration increases, the work function of the Li_xRuO₂ (110) plane significantly decrease, which highlights the



effective modification of electronic structure of RuO_2 through Li^+ insertion. Such modification facilitates electron transfer from the catalyst to the reaction intermediates, thereby enhancing the ORR and OER kinetics. Fig. S9† shows the Bader charges of Ru and O, with increasing Li^+ concentration, the acquired electron of O increases, while the donated electrons of Ru gradually reduce. It indicates a decline in the valence state of Ru cations, which aligns with the XPS results. The shift in the surface electronic structure can be attributed to the strain effect, which plays a crucial role in modulating electrocatalytic activity.^{41–44}

Furthermore, the PDOS in RuO_2 and Li_xRuO_2 were recorded to reveal the regulating effect of Li^+ insertion on the d-band center of RuO_2 . As shown in Fig. 7a, the d-band center of Li_xRuO_2 exhibits a significantly upshift from -1.86 ($x = 0$) to 1.62 eV ($x = 0.5$), approaching the Fermi level. Meanwhile, the adsorption energy of Li_xRuO_2 toward the key LiO_2 intermediate gradually increase -3.02 eV to -3.85 eV, as depicted in Fig. 7b. Moreover, the adsorption profiles of other Li–O intermediates on RuO_2 and $\text{Li}_{0.5}\text{RuO}_2$ were calculated, as illustrated in Fig. S10.† It reveals that the adsorption energy of all Li–O intermediates on the RuO_2 (110) plane is significantly lower than that on the $\text{Li}_{0.5}\text{RuO}_2$ (110) plane, indicating that the incorporation of Li^+ strengthens the interaction between Li–O intermediates and the catalyst. Notably, the strong binding interaction, particularly between LiO_2 and $\text{Li}_{0.5}\text{RuO}_2$ cathodes, assumes a pivotal role in determining the growth route of discharge products and facilitating the OER catalytic activities.^{6,45,46} Visualizations of the differential charge density distributions (Fig. S11†) provide further support for the enhanced adsorption of catalysts towards the reaction species following Li^+ intercalation. The electron donation and accumulation between O and the catalyst surface was presented by color of cyan and yellow, respectively. Remarkably, there are fewer electrons transferred from Ru to O on the RuO_2 surface

compared to the $\text{Li}_{0.5}\text{RuO}_2$ (110) surface. Based on the aforementioned calculation results, Fig. 7c presents a schematic illustrating the enhanced catalytic performance of RuO_2 with Li^+ insertion. Specifically, the remarkable improvement in electron transfer ability and adsorption functionality could synergistically optimize the reaction pathways and kinetics of the ORR and OER in Li– O_2 batteries.

Integrating computational calculation with experimental results, we have elucidated the crucial role of the pre-lithiation RuO_2 catalyst in promoting the nucleation and growth of Li_2O_2 . Typically, upon ORR, dissolved oxygen initially undergoes a one-electron reduction process, forming LiO_2 intermediate. For the RuO_2 cathode with weak adsorption, a large number of soluble intermediates were formed at the initial stage of discharge and captured by porous electrodes. As the discharge process advanced, the intermediates distributed uniform crystal seeds into the porous structure, and finally induced the growth of film-shaped Li_2O_2 in accordance with SEM observation.⁴⁷ However, for the Li_xRuO_2 cathode, Li_2O_2 growth occurs through dual growth pathways with distinct morphologies. Specifically, a film-like Li_2O_2 similar to that on the RuO_2 cathode is formed on the CNT surface. Additionally, due to the high affinity between LiO_2 and Li_xRuO_2 configurations, a significant confinement effect leads to the formation of rod-like Li_2O_2 products.¹¹ Furthermore, the charge density distribution shown in Fig. S12† indicates that even when the $\text{Li}_{0.5}\text{RuO}_2$ surface is covered by Li_2O_2 , $\text{Li}_{0.5}\text{RuO}_2$ still exhibits strong interactions with LiO_2 . Consequently, $\text{Li}_{0.5}\text{RuO}_2$ -based batteries can sustain discharge, resulting in a larger discharge capacity. During the subsequent charging process, the enhanced interaction between $\text{Li}_{0.5}\text{RuO}_2$ and LiO_2 intermediates, as well as Li_2O_2 products, facilitate the charge transfer between oxygen-containing species and oxygen electrode, thereby the OER kinetics. As a result, the discharge products can be decomposed at an ultra-low charging potential, while preventing the accumulation of residue from the discharge process and ensuring the ultralong cycle life for Li– O_2 batteries.

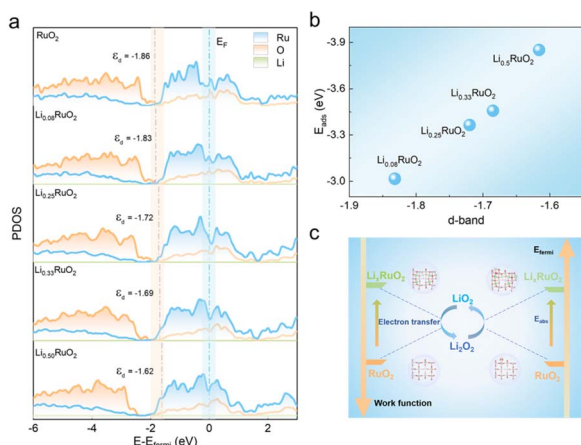


Fig. 7 (a) The partial density of states (PDOS) of the Li_xRuO_2 ($x = 0, 0.08, 0.25, 0.33, 0.5$) and the corresponding d-band center of Ru atom. (b) The variation in the adsorption energy of LiO_2 on different Li_xRuO_2 surfaces as a function of the d-band center. (c) Schematic illustration for the improved catalytic performance of RuO_2 by Li^+ insertion.

Conclusions

In this study, we synthesized a series of Li_xRuO_2 catalysts with tunable Li^+ concentrations *via* electrochemical methods. Results demonstrated that Li^+ is inserted into the octahedral interstices of RuO_2 , inducing lattice strain effect. Furthermore, the Li^+ intercalation precisely customized the surface electronic structure of Li_xRuO_2 . Specifically, Li^+ ions acted as potent electron donors, effectively reducing the valence state of Ru cations, which also results in the formation of oxygen vacancies. Benefitting from these characteristics, the charge transfer and adsorption strength between Li_xRuO_2 and oxygen-containing intermediates were synergistically strengthened, which dramatically enhanced the electrochemical performance Li– O_2 batteries. Particularly, the $\text{Li}_{0.52}\text{RuO}_2$ -based Li– O_2 battery exhibited an energy conversion efficiency of up to 80%, a long-term lifespan of 321 cycles, a high discharge capacity of $14\ 760\ \text{mA h g}^{-1}$, and desirable rate performance. This study not only presents a facile and controllable method for synthesizing



highly efficient catalysts for Li–O₂ batteries with atomic-level precision but also offers profound insights into the fundamental understanding of catalytic mechanisms, which demonstrates a promising avenue for the practical implementation of advanced energy conversion and storage systems.

Data availability

The original data supporting this article are available in the main context and ESI.†

Author contributions

Zhengcai Zhang: writing – original draft, investigation, visualization. Dulin Huang: investigation, validation, visualization. Shuochao Xing: investigation, methodology, validation, visualization. Minghui Li: investigation. Jing Wu: investigation. Zhang Zhang: writing – review & editing, supervision. Yaying Dou: writing – review & editing, supervision, funding acquisition, conceptualization. Zhen Zhou: writing – review & editing, supervision, conceptualization.

Conflicts of interest

The authors declare no competing financial interests.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (22202182), the Key R&D and Promotion Special (Scientific Problem Tackling) Project of Henan Province (242102240088) and the China postdoctoral science foundation (2023M733211).

Notes and references

- X. Chi, M. Li, J. Di, P. Bai, L. Song, X. Wang, F. Li, S. Liang, J. Xu and J. Yu, A highly stable and flexible zeolite electrolyte solid-state Li–air battery, *Nature*, 2021, **592**, 551–557.
- W.-J. Kwak, Rosy, D. Sharon, C. Xia, H. Kim, L. R. Johnson, P. G. Bruce, L. F. Nazar, Y.-K. Sun, A. A. Frimer, M. Noked, S. A. Freunberger and D. Aurbach, Lithium–Oxygen Batteries and Related Systems: Potential, Status, and Future, *Chem. Rev.*, 2020, **120**, 6626–6683.
- J. Zhang, Y. Zhao, B. Sun, Y. Xie, A. Tkacheva, F. Qiu, P. He, H. Zhou, K. Yan, X. Guo, S. Wang, A. M. McDonagh, Z. Peng, J. Lu and G. Wang, A long-life lithium–oxygen battery via a molecular quenching/mediating mechanism, *Sci. Adv.*, 2022, **8**, eabm1899.
- X. Han, L. Zhao, J. Wang, Y. Liang and J. Zhang, Delocalized Electronic Engineering of Ni₅P₄ Nanoroses for Durable Li–O₂ Batteries, *Adv. Mater.*, 2023, **35**, 2301897.
- Y. Zhou, Q. Gu, K. Yin, L. Tao, Y. Li, H. Tan, Y. Yang and S. Guo, Cascaded orbital–oriented hybridization of intermetallic Pd₃Pb boosts electrocatalysis of Li–O₂ battery, *Proc. Natl. Acad. Sci. U.S.A.*, 2023, **120**, e2301439120.
- P. Wang, Y. Ren, R. Wang, P. Zhang, M. Ding, C. Li, D. Zhao, Z. Qian, Z. Zhang, L. Zhang and L. Yin, Atomically dispersed cobalt catalyst anchored on nitrogen-doped carbon nanosheets for lithium–oxygen batteries, *Nat. Commun.*, 2020, **11**, 1576.
- Y. He, L. Ding, J. Cheng, S. Mei, X. Xie, Z. Zheng, W. Pan, Y. Qin, F. Huang, Y. Peng and Z. Deng, A “Trinity” Design of Li–O₂ Battery Engaging the Slow-Release Capsule of Redox Mediators, *Adv. Mater.*, 2023, **35**, 2308134.
- Y. Dou, X.-G. Wang, D. Wang, Q. Zhang, C. Wang, G. Chen, Y. Wei and Z. Zhou, Tuning the structure and morphology of Li₂O₂ by controlling the crystallinity of catalysts for Li–O₂ batteries, *Chem. Eng. J.*, 2021, **409**, 128145.
- B. Sun, X. Huang, S. Chen, P. Munroe and G. Wang, Porous Graphene Nanoarchitectures: An Efficient Catalyst for Low Charge-Overpotential, Long Life, and High Capacity Lithium–Oxygen Batteries, *Nano Lett.*, 2014, **14**, 3145–3152.
- J. Tian, Y. Rao, W. Shi, J. Yang, W. Ning, H. Li, Y. Yao, H. Zhou and S. Guo, Sabatier Relations in Electrocatalysts Based on High-entropy Alloys with Wide-distributed d-band Centers for Li–O₂ Batteries, *Angew. Chem., Int. Ed.*, 2023, **62**, e202310894.
- Z. Lian, Y. Lu, S. Zhao, Z. Li and Q. Liu, Engineering the Electronic Interaction between Atomically Dispersed Fe and RuO₂ Attaining High Catalytic Activity and Durability Catalyst for Li–O₂ Battery, *Adv. Sci.*, 2023, **10**, 2205975.
- Y. Dou, S. Xing, Z. Zhang and Z. Zhou, Solving the Singlet Oxygen Puzzle in Metal–O₂ Batteries: Current Progress and Future Directions, *Electrochem. Energy Rev.*, 2024, **7**, 6.
- Q. Xia, D. Li, L. Zhao, J. Wang, Y. Long, X. Han, Z. Zhou, Y. Liu, Y. Zhang, Y. Li, A. A. Adam and S. Chou, Recent advances in heterostructured cathodic electrocatalysts for non-aqueous Li–O₂ batteries, *Chem. Sci.*, 2022, **13**, 2841–2856.
- Y. Zhou, Q. Gu, Y. Xin, X. Tang, H. Wu and S. Guo, Orbital Coupling of PbO₇ Node in Single-Crystal Metal–Organic Framework Enhances Li–O₂ Battery Electrocatalysis, *Nano Lett.*, 2023, **23**, 10600–10607.
- Z. Sun, X. Zhao, W. Qiu, B. Sun, F. Bai, J. Liu and T. Zhang, Unlock Restricted Capacity via O–Ce Hybridization for Li–Oxygen Batteries, *Adv. Mater.*, 2023, **35**, 2210867.
- R. Zheng, D. Du, Y. Yan, S. Liu, X. Wang and C. Shu, Cation Vacancy Modulated Interfacial Electronic Interactions for Enhanced Electrocatalysis in Lithium–Oxygen Batteries, *Adv. Funct. Mater.*, 2024, 2316440, DOI: [10.1002/adfm.202316440](https://doi.org/10.1002/adfm.202316440).
- Z. Shen, W. Yu, A. Aziz, K. Chida, T. Yoshii and H. Nishihara, Sequential Catalysis of Defected-Carbon and Solid Catalyst in Li–O₂ Batteries, *J. Phys. Chem. C*, 2023, **127**, 6239–6247.
- Q. Lu, X. Zou, X. Wang, L. An, Z. Shao and Y. Bu, Simultaneous reactant accessibility and charge transfer engineering in Co-doped RuO₂-supported OCNT for robust rechargeable zinc–air batteries, *Appl. Catal., B*, 2023, **325**, 122323.
- S. Wang, M. Lu, X. Xia, F. Wang, X. Xiong, K. Ding, Z. Pang, G. Li, Q. Xu, H.-Y. Hsu, S. Hu, L. Ji, Y. Zhao, J. Wang, X. Zou and X. Lu, A universal and scalable transformation of bulk



- metals into single-atom catalysts in ionic liquids, *Proc. Natl. Acad. Sci. U.S.A.*, 2024, **121**, e2319136121.
- 20 H. Li, X. Han, W. Zhao, A. Azhar, S. Jeong, D. Jeong, J. Na, S. Wang, J. Yu and Y. Yamauchi, Electrochemical preparation of nano/micron structure transition metal-based catalysts for the oxygen evolution reaction, *Mater. Horiz.*, 2022, **9**, 1788–1824.
- 21 D. Gao, H. Li, P. Wei, Y. Wang, G. Wang and X. Bao, Electrochemical synthesis of catalytic materials for energy catalysis, *Chin. J. Catal.*, 2022, **43**, 1001–1016.
- 22 S. Jiang, H. Suo, X. Zheng, T. Zhang, Y. Lei, Y.-X. Wang, W.-H. Lai and G. Wang, Lightest Metal Leads to Big Change: Lithium-Mediated Metal Oxides for Oxygen Evolution Reaction, *Adv. Energy Mater.*, 2022, **12**, 2201934.
- 23 J. Park, H. Kim, K. Jin, B. J. Lee, Y.-S. Park, H. Kim, I. Park, K. D. Yang, H.-Y. Jeong, J. Kim, K. T. Hong, H. W. Jang, K. Kang and K. T. Nam, A New Water Oxidation Catalyst: Lithium Manganese Pyrophosphate with Tunable Mn Valency, *J. Am. Chem. Soc.*, 2014, **136**, 4201–4211.
- 24 K. Jiang, H. Wang, W.-B. Cai and H. Wang, Li Electrochemical Tuning of Metal Oxide for Highly Selective CO₂ Reduction, *ACS Nano*, 2017, **11**, 6451–6458.
- 25 S. Zhang, S. Gu, Y. Wang, C. Liang, Y. Yu, L. Han, S. Zheng, N. Zhang, X. Liu, J. Zhou and J. Li, Spontaneous Delithiation under Operando Condition Triggers Formation of an Amorphous Active Layer in Spinel Cobalt Oxides Electrocatalyst toward Oxygen Evolution, *ACS Catal.*, 2019, **9**, 7389–7397.
- 26 Y. Hu, T. Zhang, F. Cheng, Q. Zhao, X. Han and J. Chen, Recycling Application of Li-MnO₂ Batteries as Rechargeable Lithium-Air Batteries, *Angew. Chem., Int. Ed.*, 2015, **54**, 4338–4343.
- 27 G. Kresse and J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169–11186.
- 28 S. Grimme, S. Ehrlich and L. Goerigk, Effect of the damping function in dispersion corrected density functional theory, *J. Comput. Chem.*, 2011, **32**, 1456–1465.
- 29 P. E. Blöchl, Projector augmented-wave method, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **50**, 17953–17979.
- 30 S. Grimme, J. Antony, S. Ehrlich and H. Krieg, A consistent and accurate ab initio parametrization of density functional dispersion correction (DFT-D) for the 94 elements H-Pu, *J. Chem. Phys.*, 2010, **132**, 154104.
- 31 V. Wang, N. Xu, J.-C. Liu, G. Tang and W.-T. Geng, VASPKIT: A user-friendly interface facilitating high-throughput computing and analysis using VASP code, *Comput. Phys. Commun.*, 2021, **267**, 108033.
- 32 K. Momma and F. Izumi, VESTA 3 for three-dimensional visualization of crystal, volumetric and morphology data, *J. Appl. Crystallogr.*, 2011, **44**, 1272–1276.
- 33 P. Balaya, H. Li, L. Kienle and J. Maier, Fully Reversible Homogeneous and Heterogeneous Li Storage in RuO₂ with High Capacity, *Adv. Funct. Mater.*, 2003, **13**, 621–625.
- 34 A. S. Hassan, A. Navulla, L. Meda, B. R. Ramachandran and C. D. Wick, Molecular Mechanisms for the Lithiation of Ruthenium Oxide Nanoplates as Lithium-Ion Battery Anode Materials: An Experimentally Motivated Computational Study, *J. Phys. Chem. C*, 2015, **119**, 9705–9713.
- 35 D. J. Morgan, Resolving ruthenium: XPS studies of common ruthenium materials, *Surf. Interface Anal.*, 2015, **47**, 1072–1079.
- 36 M. Hu, T. Yu, K. Tan, A. Zhou, L. Luo and S. Yin, Ultralow Ru loading RuO₂-TiO₂ with strong oxide-support interaction for efficient chlorine evolution and ammonia-nitrogen-elimination, *Chem. Eng. J.*, 2023, **465**, 143001.
- 37 G. Li, T. Sun, H.-J. Niu, Y. Yan, T. Liu, S. Jiang, Q. Yang, W. Zhou and L. Guo, Triple Interface Optimization of Ru-based Electrocatalyst with Enhanced Activity and Stability for Hydrogen Evolution Reaction, *Adv. Funct. Mater.*, 2023, **33**, 2212514.
- 38 Y. Li, T. Xu, Q. Huang, L. Zhu, Y. Yan, P. Peng and F.-F. Li, C60 Fullerenol to Stabilize and Activate Ru Nanoparticles for Highly Efficient Hydrogen Evolution Reaction in Alkaline Media, *ACS Catal.*, 2023, **13**, 7597–7605.
- 39 B. Sun, L. Guo, Y. Ju, P. Munroe, E. Wang, Z. Peng and G. Wang, Unraveling the catalytic activities of ruthenium nanocrystals in high performance aprotic Li-O₂ batteries, *Nano Energy*, 2016, **28**, 486–494.
- 40 Z. Liang, Q. Zou, J. Xie and Y.-C. Lu, Suppressing singlet oxygen generation in lithium-oxygen batteries with redox mediators, *Energy Environ. Sci.*, 2020, **13**, 2870–2877.
- 41 S. Schnur and A. Groß, Strain and coordination effects in the adsorption properties of early transition metals: A density-functional theory study, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2010, **81**, 033402.
- 42 X. Wang, Y. Orikasa, Y. Takesue, H. Inoue, M. Nakamura, T. Minato, N. Hoshi and Y. Uchimoto, Quantitating the Lattice Strain Dependence of Monolayer Pt Shell Activity toward Oxygen Reduction, *J. Am. Chem. Soc.*, 2013, **135**, 5938–5941.
- 43 A. M. Smith, A. M. Mohs and S. Nie, Tuning the optical and electronic properties of colloidal nanocrystals by lattice strain, *Nat. Nanotechnol.*, 2009, **4**, 56–63.
- 44 K. Wang, K. Yu, S. Xu, S. Yuan, L. Xiang, B. Pang, J. Zheng and N. Li, Synergizing lattice strain and electron transfer in TMSs@1T-MoS₂ in-plane heterostructures for efficient hydrogen evolution reaction, *Appl. Catal., B*, 2023, **328**, 122445.
- 45 Q. Lv, Z. Zhu, Y. Ni, J. Geng and F. Li, Spin-State Manipulation of Two-Dimensional Metal-Organic Framework with Enhanced Metal-Oxygen Covalency for Lithium-Oxygen Batteries, *Angew. Chem., Int. Ed.*, 2022, **61**, e202114293.
- 46 L.-N. Song, W. Zhang, Y. Wang, X. Ge, L.-C. Zou, H.-F. Wang, X.-X. Wang, Q.-C. Liu, F. Li and J.-J. Xu, Tuning lithium-peroxide formation and decomposition routes with single-atom catalysts for lithium-oxygen batteries, *Nat. Commun.*, 2020, **11**, 2191.
- 47 Z. Gou, Y. Yao, X. Geng, F. Yang, X. Hu, Z. Chen, L. Zheng, Y. Su, F. Wu and J. Lu, Dual Redox Mediators Assisted Hierarchically Porous Hollow Carbon Shell Cathode for Enhanced Performance Li-O₂ Battery, *Adv. Energy Mater.*, 2024, 2304272, DOI: [10.1002/aenm.202304272](https://doi.org/10.1002/aenm.202304272).

