



**Materials
Horizons**

Heterojunction Bilayers Serving as a Charge Transporting Interlayer to Reduce the Dark Current and Enhance Photomultiplication in Organic Shortwave Infrared Photodetectors

Journal:	<i>Materials Horizons</i>
Manuscript ID	MH-COM-04-2022-000479.R1
Article Type:	Communication
Date Submitted by the Author:	24-May-2022
Complete List of Authors:	Shin, Chanho; University of California San Diego, Materials Science and Engineering Program Li, Ning; University of California San Diego, Department of Electrical and Computer Engineering Seo, Bogyom; University of California San Diego, Department of Electrical and Computer Engineering Eedegurala, Naresh; University of Southern Mississippi Azoulay, Jason; University of Southern Mississippi, School of Polymers and High Performance Materials Ng, Tse Nga; University of California San Diego, Department of Electrical and Computer Engineering

SCHOLARONE™
Manuscripts

New Concepts:

Photomultiplication detectors are promising for overcoming the low responsivity in organic shortwave infrared photodetectors. However, recent photomultiplication detectors often increase both the responsivity and dark current, which nullifies the effect on detectivity. To suppress the dark current in photomultiplicative devices, we present a new interlayer structure, a pn junction combination that overcomes the trade-off between signal and noise. Our bilayer design demonstrate the advantages in reduced dark current and excellent external quantum efficiency compared to devices using typical unipolar charge-transporting materials. We incorporated this new interlayer design in upconversion imagers, doubling the upconversion efficiency and image contrast. This interlayer is generalizable to different organic semiconductors, which are especially useful as the design here will be applicable to future infrared materials yet to be discovered.

Heterojunction Bilayers Serving as a Charge Transporting Interlayer to Reduce the Dark Current and Enhance Photomultiplication in Organic Shortwave Infrared Photodetectors

Chanho Shin¹, Ning Li², Bogyom Seo², Naresh, Eedugurala³, Jason D. Azoulay³, Tse Nga Ng^{1,2*}

¹ Department of Material Science and Engineering Program, University of California San Diego, 9500 Gilman Drive, La Jolla, CA 92093-0407, United States.

² Department of Electrical and Computer Engineering, University of California San Diego, 9500 Gilman Drive, La Jolla, CA 92093-0407, United States.

³ School of Polymer Science and Engineering, University of Southern Mississippi, 118 College Drive #5050, Hattiesburg, MS 39406, United States.

*Email: tnn046@ucsd.edu

Abstract

Previous approaches to induce photomultiplication in organic diodes have increased the photosignal but lacked control over reducing background noise. This work presents a new interlayer design based on a heterojunction bilayer that concurrently enables photomultiplication and suppresses the dark current in organic shortwave infrared detectors to improve the overall detectivity. The heterojunction bilayer is consisted of a hole-transporting material copper thiocyanate and an electron-transporting material tin oxide, and this combination offers the ability to block charge injection in the dark. Under illumination, the bilayer promotes trap-assisted photomultiplication by lowering the tunneling barrier and amplifying the photocurrent through injection of multiple carriers per absorbed photon. Upon incorporating the heterojunction interlayer in photodiodes and upconversion imagers to trigger photomultiplication, the devices achieve an external quantum efficiency up to 560% and a detectivity of 3.5×10^9 Jones, and the upconversion efficiency of the imager is doubled with 1.7x improvement in contrast compared to the imager without the heterojunction interlayer. The new interlayer design is generalizable to work with different organic semiconductors, making it attractive and easy to integrate with emerging organic infrared systems.

Keywords

heterojunction, organic photodiode, dark current noise, photomultiplication, upconversion

Introduction

Organic photodetectors responsive to shortwave infrared (SWIR) radiation^{1,2} are emerging, as organic semiconductors facilitate direct integration and new form factors that would improve the spatial resolution of imagers.³⁻⁷ Since the detectivity, namely the signal-to-noise ratio, of organic SWIR detectors is still lower than conventional inorganic counterparts,

recent research has deployed photomultiplication mechanisms to increase the device response.⁸ In trap-assisted photomultiplication, the charge injection barrier is lowered through an accumulation of photogenerated charges, leading to multiple charges being injected per photon absorbed and resulting in an external quantum efficiency greater than 100%. While successful at amplifying light signals, prior approaches have limited control over reducing dark current noises. To address this challenge, here we examine a new interface design that simultaneously suppresses the dark current^{9–13} and enables photomultiplication to improve the overall detectivity in organic SWIR devices.

Previous organic photomultiplication devices can be categorized into two types, either modifying 1) the bulk heterojunction (BHJ) layer or 2) the charge transporting interlayers next to electrodes. For the first type,^{14–17} the ratio between donor and acceptor materials is tuned to be dominated by one material ranging from 20:1 to 100:1, in which the minor component is isolated from electrodes and served as trap sites for photogenerated carriers to accumulate, induce band bending, and lower the charge injection barrier. This method of modifying the BHJ layer was acceptable for visible to near-infrared photodiodes; however, for SWIR devices the narrow bandgap materials are less efficient at exciton dissociation^{18,19} and require a more balanced donor-to-acceptor ratio to reduce recombination loss²⁰ and yield sufficient photogenerated charges in the first place in order to trigger photomultiplication. The second type^{21–24} of photomultiplication devices, in which interfacial layers are designed to enhance trap-assisted charge injection, does not involve a highly unbalanced BHJ composition and therefore is better suited for SWIR operation. Yet so far, the devices in this second category have been affected by high dark current upon adjustments of interlayer energy levels. Further research on interlayer designs is needed to achieve photomultiplication without a concurrent increase in the dark current.

Typically the interlayers between BHJs and electrodes are unipolar materials that regulate carrier transport as seen in **Figure 1a**. To induce photomultiplication as illustrated in **Figure 1b**, the interlayer materials are chosen to block the transport of electrons, and the trapped electrons reduce the tunnelling barrier for holes to be injected. As such the photosignal is multiplied through charge injection. However, the interlayer configuration in Figure 1b cannot block hole injection in the dark and leads to higher noise current than the conventional structure in Figure 1a.

To decouple this trade-off between the background noise and the photocurrent, we introduce a bilayer heterojunction as the interlayer between the BHJ and the charge injecting electrode as shown in **Figure 1c**. Instead of a single charge-transporting material, the interlayer is consisted of two materials with an energetic offset forming a pn junction. In the dark, hole injection is expected to be inhibited by the additional n-layer, suppressing the dark current in comparison to the configuration in Figure 1b. Meanwhile, this bilayer will enable photomultiplication under illumination, because of photogenerated electrons that are trapped

at the pn junction and consequently lower the hole injection barrier of the n-layer. We note that the order of the pn bilayer should be coordinated with respect to the applied bias. The configuration of Figure 1c places the pn bilayer at forward bias for good charge injection under light. An alternative arrangement with the layers reversed in **Figure 1d** would not trigger photomultiplication, since the trapped electrons will be too far from the n-layer and unable to effectively lower the injection barrier.

Based on the design strategy in Figure 1c, this work presents organic SWIR detectors achieving excellent photomultiplicative gain with a dark current lower than conventional photodiodes without gain. After the photodiode performance is characterized in terms of detectivity and response speed, the SWIR sensor is integrated with an organic light emitting diode to demonstrate an upconversion imager. Improvements in the upconversion efficiency are realized as a result of active photomultiplication in the sensor delivering more charges to the light emitter. This proof-of-concept demonstration shows that our new interlayer is widely applicable and compatible with different optical structures to boost the performance of organic SWIR devices.

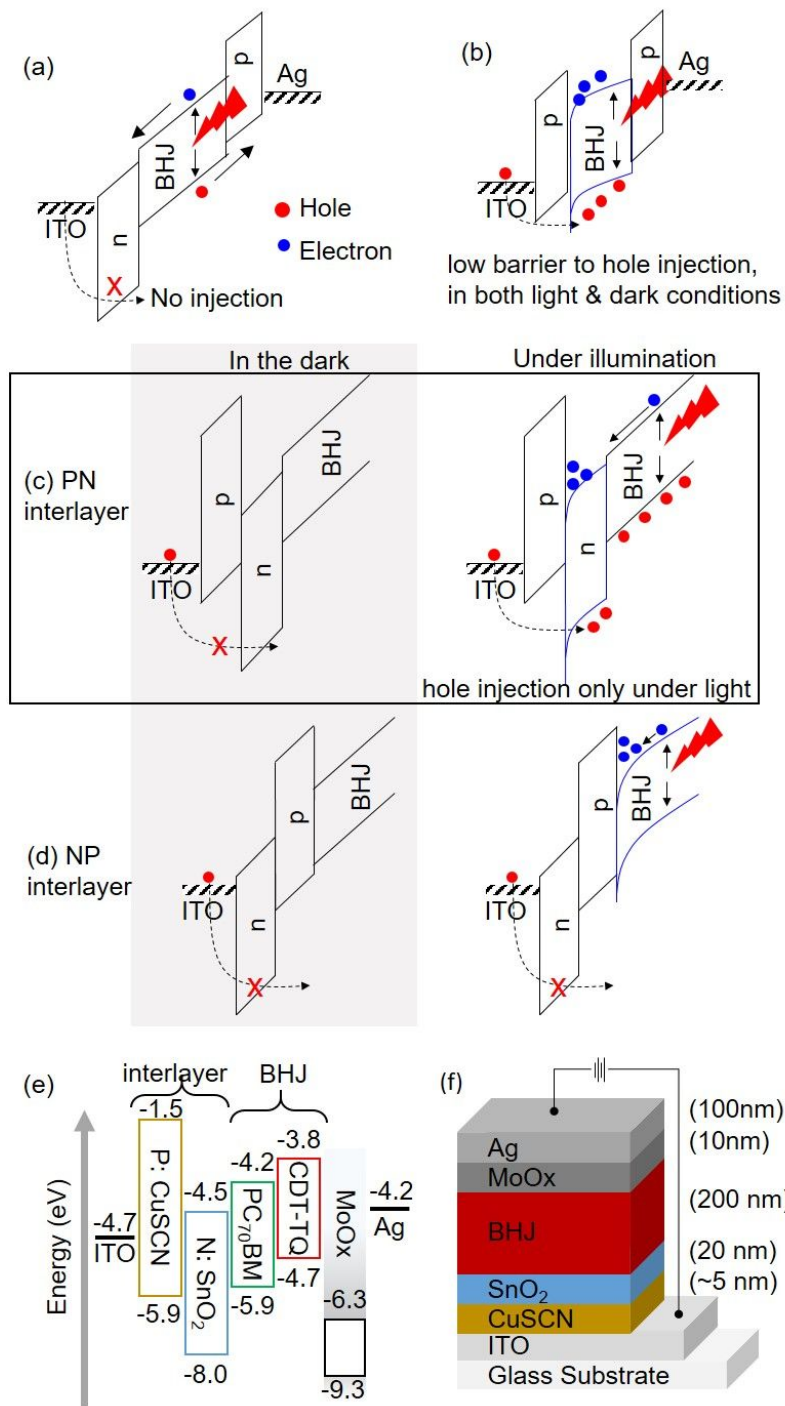


Figure 1. Interlayer designs. Energy diagrams of (a) a conventional photodiode with unipolar charge transporting interlayers and no photomultiplication and (b) a photodiode using a single charge blocking material, which induces photomultiplication but shows high noise current from charge injection in the dark. (c) Changing the interlayer over the ITO electrode to a pn heterojunction bilayer that enables photomultiplication and suppresses dark current. (d)

Reversing the p- and n-type materials in the bilayer inhibits photomultiplication. (e) Energy levels of the materials used in this work. (f) Cross-sectional layers in our photomultiplication device.

Results and Discussions

Effects of the heterojunction bilayer on photodiode performance

The materials and photodiode structure used in this work are shown in **Figure 1e**. The interlayer next to ITO was a bilayer of hole-transporting copper thiocyanate²⁵ (CuSCN) and electron-transporting tin oxide^{26–31} (SnO₂). Other materials combination with similar energy levels to CuSCN and SnO₂ are also applicable for the pn interlayer. During device operation, the indium tin oxide (ITO) electrode is under positive bias, and the pn interlayer is forward biased while the BHJ is reverse biased. Formulas for computing devices metrics are included in the Experimental Section.

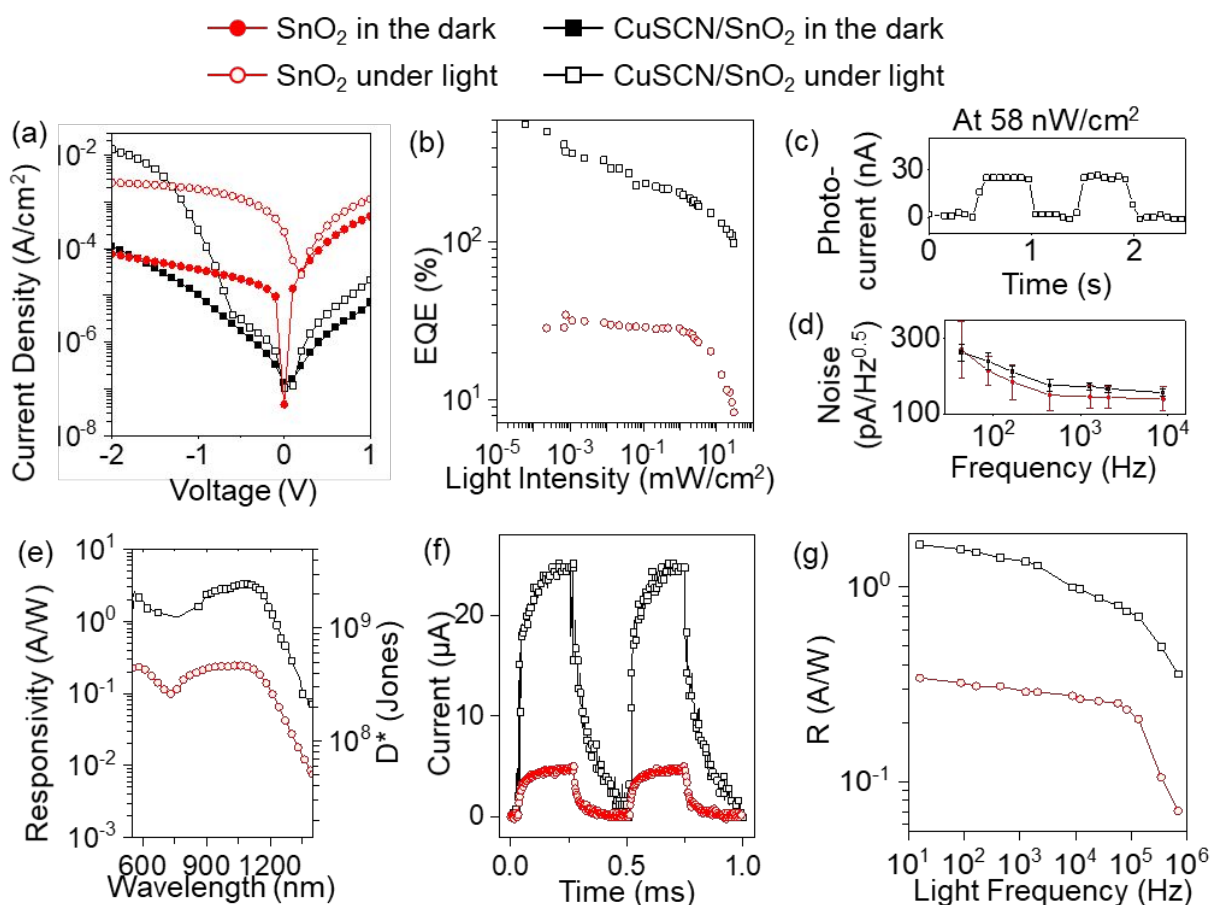


Figure 2. Comparison of the single and bilayer interlayers, with the devices biased at -1.5 V on the Ag electrode. (a) Current density versus applied voltage, measured in the dark and under 9.1 mW/cm² illumination from a 1050 nm LED. (b) External quantum efficiency taken at the wavelength of 1050 nm as a function of incident light intensity. (c) Temporal photoresponse

under 58 nW/cm^2 , with the 1050 nm LED modulated at 1 Hz. (d) Noise current as a function of measurement frequency. (e) Responsivity and specific detectivity measured at 313 Hz as a function of spectral wavelength, under $1.6 \text{ }\mu\text{W/cm}^2$ illumination. (f) Temporal photoresponse under 0.15 mW/cm^2 , with the 1050 nm LED modulated at 2077 Hz. (g) Photoresponse amplitude versus the modulation frequency of the incident light at an intensity of 0.15 mW/cm^2 from the 1050 nm LED.

Figure 2a compares the current-voltage characteristics of photodiodes with a conventional interlayer (a single n-type SnO_2 , Figure 1a) versus a pn bilayer (p: CuSCN/n: SnO_2 stack, Figures 1c and 1e). Under illumination at low applied biases $< -1.3 \text{ V}$ on the Ag electrode, the photocurrent was initially lower in the device with the bilayer than the conventional structure, because the additional CuSCN in the bilayer prevented the collection of photogenerated electrons. While trapped, the electrons bent the energy levels at the CuSCN/ SnO_2 interface and decreased the hole-injection barrier. As the applied bias was raised, hole injection increased, and eventually for a bias $> -1.3 \text{ V}$ the injected photocurrent through the bilayer stack exceeded the level measured in the conventional photodiode. The external quantum efficiency reached over 100% at -1.6 V , indicative of photomultiplication at work in the device with the bilayer.

Meanwhile, the characteristics in the dark shows a reduction in the dark current due to the bilayer compared to the conventional structure. The dark current in Figure 2a is higher than devices operating in the visible but comparable to other infrared devices responsive to SWIR wavelengths longer than $1 \text{ }\mu\text{m}$.¹¹ The reason for the high dark current in SWIR photodiodes is that the bandgap of the BHJ must be reduced in order to respond to longer wavelengths. Below -1.8 V the bilayer enabled a dark current lower than the conventional structure in Figure 1a. Since the energy difference between ITO and SnO_2 is up to 3.3 eV , we thought the single SnO_2 layer in the conventional structure would already be effective at blocking hole injection in the dark. However, the experimental observation is that adding a thin 5-nm CuSCN layer to the interlayer further reduced the dark current, and we attribute this effect as probably from the elimination of pinhole leakage paths in the bilayer stack. For a bias voltage larger than -1.8 V , the dark current of the device with bilayer increased faster than the single layer, because the applied electric field eventually reached so high that the probability of charge injection from ITO into the n- SnO_2 layer increased.³² Nonetheless, the rise in dark current was still negligible compared to the photomultiplication current. In the future, the n-type SnO_2 can be changed to a material with an energy level closer to the BHJ at the lowest unoccupied molecular orbital (LUMO) to further reduce charge injection at high electric field. With the structure in this paper, for the voltage window between -1 V and -1.8 V the device with the bilayer showed higher photocurrent while maintaining lower dark current than the device with the single SnO_2 layer.

The device external quantum efficiency (EQE) as a function of incident light intensity is shown in **Figure 2b**. The EQE of the conventional device was constant $\sim 30\%$ and independent of

light intensity until it reached saturation around 1 mW/cm^2 . In contrast, the device with the CuSCN/SnO₂ interlayer exhibited EQE's higher than 100% for light intensities below 10 mW/cm^2 . At 58 nW/cm^2 , the EQE was 560%. The EQE increased with decreasing intensities, and this trend is characteristic of a trap-assisted gain mechanism that have been observed in a variety of materials from organics to oxides to two-dimensional semiconductors.^{33–36} The photomultiplicative gain factor is proportional to $\tau_{\text{trap}}/\tau_{\text{transit}}$; when the charge transit time τ_{transit} is shorter than the trap lifetime τ_{trap} , the photocurrent is amplified by the gain factor. The lifetime of trapped charges was extended at low light intensity,³³ because photogenerated charges occupied the deep trap states first before filling up shallow trap states. Charges trapped in deep states escaped more slowly than those in shallow states and thus led to a longer trap lifetime and increasing gain factor and EQE at low light intensity.

With a higher EQE enabled by photomultiplication, the detection limit of the device with CuSCN/SnO₂ is extended to a lower light intensity than the conventional structure. The current of the device with CuSCN/SnO₂ in **Figure 2c** shows a clear photoresponse under modulated illumination at a low intensity of 58 nW/cm^2 , for which the conventional device was not capable to show a clear signal above its background noise. The measured noise of the conventional device and the one with CuSCN/SnO₂ are comparable at -1.5 V bias as seen in **Figure 2d**. In **Figure 2e** we determined the detectivity versus incident wavelength for the devices measured at a frequency of 313 Hz and with a bias of -1.5 V . At the peak of 1100 nm , the detectivity D^* reached 3.5×10^9 Jones for the device with CuSCN/SnO₂ and 6×10^8 Jones for the conventional device, under the light intensity of 58 nW/cm^2 . From the detectivity values, we calculated the noise-equivalent power (NEP), which was 1.5 nW for the device with CuSCN/SnO₂ and 8.9 nW for the conventional device.

Figure 2f shows the temporal response of the devices when the incident light was modulated at 2 kHz . The device with CuSCN/SnO₂ underwent photomultiplication, which caused a slower rise and fall time than the conventional device, since the charge injection and de-trapping processes would prolong the response time for the device to reach steady state. The frequency response of the devices is compared in **Figure 2g**, in which the signal amplitudes dropped to -3 dB at 30 kHz for the device with CuSCN/SnO₂ and 100 kHz for the conventional device. The gain-bandwidth product is $2.6 \times 10^5 \text{ Hz A W}^{-1}$ for the devices, and the trade-off in speed with gain is typical for photomultiplication devices.

Integration of the bilayer heterojunction to improve upconversion imagers

Following successful improvements on individual photodiodes, we extended the heterojunction bilayer design to enhance SWIR upconversion imagers for demonstrating the generalizability of this new interlayer in different applications. Upconversion imagers^{37–41} locally convert low-energy infrared photons absorbed by the photodetector layer into high-energy visible photons in the light emitter layer, thus serving as a compact visualization tool for infrared

radiation. However, the photon-to-photon efficiency (η_{p-p}) of upconversion imagers is still limited⁴² and hinders the production of high-quality images. Applying photomultiplication in the upconversion process would increase charge injection into the emitter and raise its luminance, but this approach has only been demonstrated only for the near-infrared range or with quantum-dot materials. Below we show the feasibility of applying our heterojunction bilayer to induce photomultiplication in SWIR ranges and increase the efficiency of organic upconversion imagers.

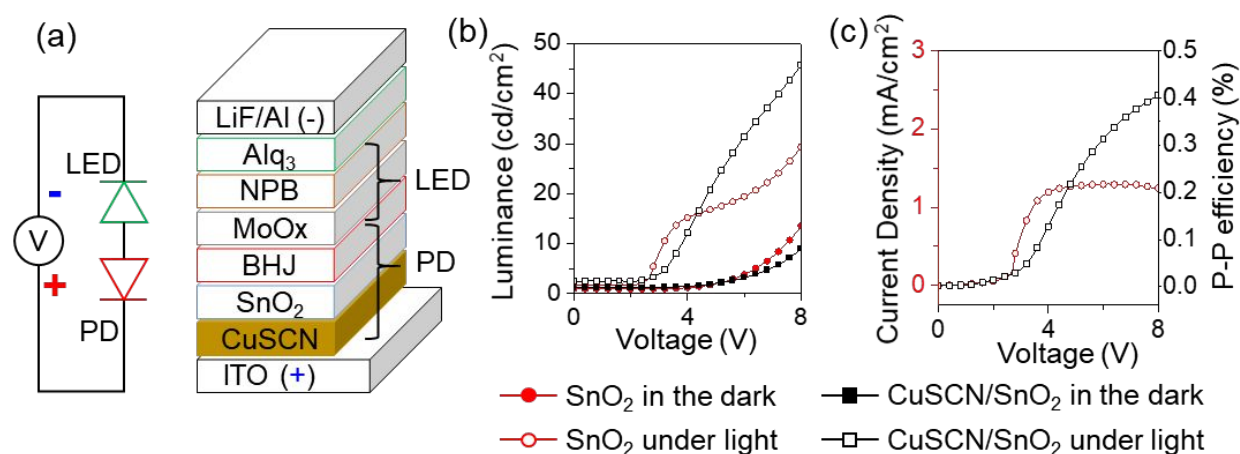


Figure 3. Upconversion imagers with different interlayers in the photodiode stack. The incident light was at an intensity of 5 mW/cm² from a 1050 nm light source. (a) Schematics of the upconversion imager with the CuSCN/SnO₂ bilayer. (b) Luminance of the visible light emitted from the imager versus the applied bias. (c) Current density and photon-to-photon upconversion efficiency versus the applied bias.

Figure 3a shows the schematic of our organic upconversion imager, which is an integrated structure of a photodiode (PD) and a light-emitting diode (LED) arranged as back-to-back diodes. We compare the effect of changing the PD interlayer on the upconverted light output in **Figure 3b**. In the dark, the luminance was reduced for the device with the CuSCN/SnO₂ interlayer, which was helpful for improving the imager contrast between regions of active upconversion and background emission. Under an illumination of 5 mW/cm² at 1050 nm, as the applied bias was increased, the device with CuSCN/SnO₂ leveraged photomultiplication to increase charge injection into the emitter, and its luminance surpassed the conventional structure with only SnO₂ for biases over 4.4 V. In **Figure 3c**, the device current densities corresponding to the luminance outputs show that there was 2 times higher current running through the photomultiplication device than the conventional device at 8 V. As a result, the η_{p-p} efficiency of the imager was doubled from 0.2% to 0.4% by changing the PD interlayer from only SnO₂ to the bilayer CuSCN/SnO₂.

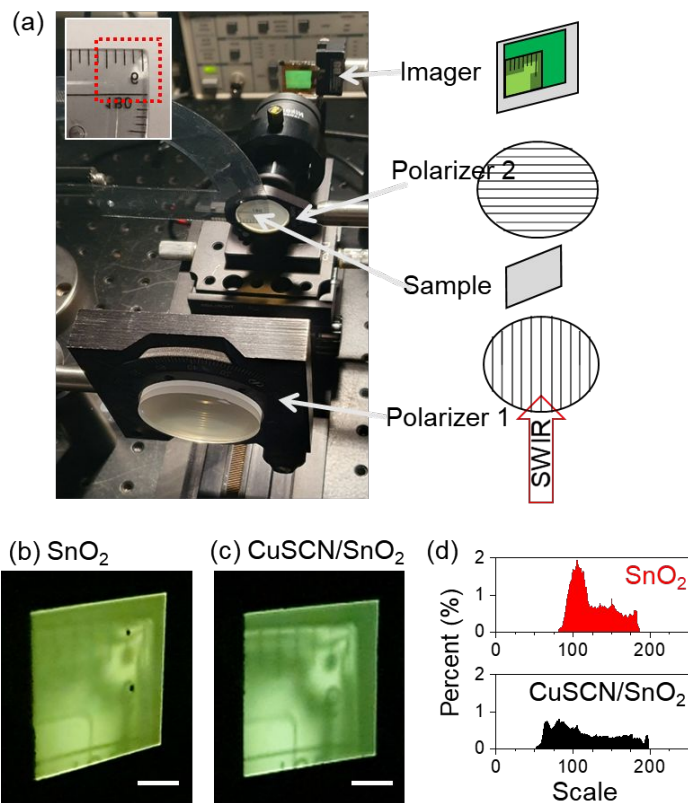


Figure 4. Results of upconversion images. (a) Imaging setup. The red box on the plastic protractor indicates the area being imaged. Upconversion images produced by (b) the imager with conventional interlayer and (d) the imager with the heterojunction interlayer. The scale bar represents 5 mm. The imagers were operated at 5 V, and the sample was under $290 \mu\text{W}/\text{cm}^2$ illumination from a 940 nm LED. (d) Histograms of images in parts (b) and (c).

To compare the quality of upconversion images, the two imagers with different interlayers were used to visualize stress gradients in a sample placed between polarization filters as shown in **Figure 4a**. The sample was a plastic protractor, and for plastics made by injection molding, there would usually be stress gradients prominent at corners and edges due to different materials flow rate in the fabrication process. Local stress variations would be shown as bright and dark regions depending on whether the refracted light from the sample aligned with the polarization filter in front of the imager. In **Figures 4b** and **4c**, the sample image by the imager with $\text{CuSCN}/\text{SnO}_2$ shows better contrast than that with only SnO_2 as the interlayer. Using the image analysis software ImageJ under the RGB stack function, the contrast between the peak light level to the background is 3.9 for the former photomultiplication device and 2.3 for the latter, indicating improved quality through the interlayer modification. While the histograms in **Figure 4d** are limited to 256 levels due to the image conversion process, the contrast increased by 1.7 times.

Conclusion

This work has demonstrated the performance of a bilayer heterojunction CuSCN/SnO₂ as the charge transporting interlayer in organic SWIR photodetectors to realize photomultiplication and low dark current, with an EQE up to 560% and a detectivity of 3.5×10^9 Jones. As the bilayer was applied to upconversion imagers, the upconversion efficiency and imager contrast was nearly doubled compared to the conventional structure. The bilayer heterojunction design can be further optimized; for example, the thickness of the SnO₂ layer is currently set at 20 nm to be the same in the control and the new bilayer, but it is possible that this layer thickness can be slightly reduced in the bilayer without impacting the dark current. A thinner bilayer can increase charge injection during the photomultiplication process to reach for higher amplification. Modifying the interlayer to enhance photomultiplication offers a key advantage that it is adaptable to different BHJ choices, making it versatile and compatible with future semiconductor materials that can extend the spectral range and functionalities of organic infrared detectors.

Experimental Procedures

Materials

The synthesis of the polymer (poly(4-(5-(4-(3,5-bis(dodecyloxy)benzylidene)-4H-cyclopenta[2,1-b:3,4-b']dithiophen-2-yl)thiophen-2-yl)-6,7-dioctyl-9-(thiophen-2-yl)-[1,2,5]thiadiazolo[3,4-g]quinoxaline)) (CDT-TQ) was described in Ref. ⁴³, and the polymer belonged to a class of narrow bandgap donor-acceptor copolymers.⁴⁴ The acceptor [6,6]-phenyl-C71-butyric acid methyl ester (PC₇₀BM) was purchased from Ossila Ltd. Camphoric acid anhydride (CA), which is used to increase the dielectric constant of the BHJ layer to enhance exciton dissociation,⁴³ was purchased from Sigma-Aldrich Ltd. The CDT-TQ, PC₇₀BM, and CA were blended at 2:4:1 weight ratio dissolved in 1,2-dichlorobenzene at a concentration of 28 mg mL⁻¹. An additive 1,8-diiodooctane was added to the blend at a volume ratio of 3%. This BHJ blend solution was stirred at 70 °C for at least 24 hours. The solution for the CuSCN layer was prepared by dissolving CuSCN in diethyl sulphide at a concentration of 2 mg mL⁻¹. We have varied the concentration of the CuSCN solution from 1.5 to 2 mg mL⁻¹. It is found that 2 mg mL⁻¹ is the lowest concentration for CuSCN processing. If the solution concentration is lower than 2 mg mL⁻¹, the sample showed non-uniform coverage of the film. The solution for electron-transporting SnO₂ was prepared by dissolving SnCl₂.H₂O in ethanol at concentration of 0.07 M, and the solution⁴⁵ was stirred in water bath at 80 °C for 4 hours followed by 40 °C for another 4 hours.

Photodiode fabrication

The ITO substrates with a sheet resistance $\sim 15 \Omega \text{ sq}^{-1}$ were cleaned by detergent, deionized water, acetone, and isopropanol, submerged in each solvent for 15 min sonication. For device having SnO₂ single layer, the SnO₂ layer was prepared by spin-coating the precursor

solution at 3000 rpm for 40 s. The sample was annealed at 180 °C for 1 hour, resulting in a thin film of ~20 nm. For device having CuSCN /SnO₂ bilayer, the CuSCN layer was prepared by spin-coating the solution at 1200 rpm for 40s and then annealing at 90°C for 5 min in the ambient, resulting in a thin film of ~5 nm. The SnO₂ layer was prepared by spin-coating the precursor solution at 3000 rpm for 40 s and annealing up to 170 °C for 1 hour. The substrates with interlayers were transferred to a nitrogen-filled glovebox to deposit the BHJ layer. The BHJ blend solution was spin-coated at 2000 rpm for 40 s on top of the SnO₂ layer to form a film with a thickness of ~200 nm. Afterwards, 10 nm molybdenum oxide (MoOx) and 100nm Ag layer were thermally deposited through a shadow mask, defining an active area of 0.09 cm². All the devices were encapsulated before characterization in the ambient.

Photodiode characterization

In the current-voltage measurements, the bias voltage was applied by a sourcemeter (Keithley 2400), and the current was recorded by the same sourcemeter. SWIR light was from a LED (Thorlabs, LED1050L) with a peak wavelength of 1050 nm. The light intensity was controlled by adjusting the distance between device and LED and measured by a germanium (Ge) detector (Newport, 818IR). In the EQE measurements, the monochromatic light source was modulated at 313 Hz by an optical chopper. The device photocurrent was amplified through a pre-amplifier (Stanford Research Systems, SRS 570) and then recorded by a lock-in amplifier (Stanford Research Systems, SR 530). The noise spectral densities were measured using the pre-amplifier connected to the lock-in amplifier. The reference frequency in the noise current measurements was controlled by a function generator (Rigol, DG 2401A) serving as the external trigger for the lock-in amplifier. The device noise was calculated by subtracting the equipment background noise. Transient photocurrent was measured under the 1050 nm LED light modulated by the function generator, and the corresponding photocurrent was recorded by an oscilloscope (Rigol, DS1054).

The external quantum efficiency was calculated from the photocurrent:

$$EQE = (J_{ph}/P_{illum}) (hc/\lambda q) = R(hc/\lambda q), \quad (1)$$

where J_{ph} is the photocurrent density, P_{illum} is the intensity of the incident light, h is the Plank's constant, c is the speed of light, λ is the wavelength of the incident light, and q is the elementary charge, and R is the responsivity.

The specific detectivity was determined by

$$D^* = RA^{0.5}/S_n, \quad (2)$$

where R is the responsivity (A/W), A is the photodetector active area (cm²), and S_n is the noise spectral density (A/Hz^{0.5}) of the detector.

The noise equivalent power is wavelength dependent and related to detectivity by

$$NEP = A^{0.5}/D^* = P_{min}/\sqrt{BW}, \quad (3)$$

where P_{min} is the minimum detectable optical power and BW is the measurement bandwidth.

Upconversion imager fabrication and characterization

For the upconversion imager, additional layers were deposited on top of the PD layers following the schematic in Figure 3a. The films of 35 nm N,N'-Bis(naphthalen-1-yl)-N,N'-bis(phenyl)benzidine (NPB), 50 nm tris(8-hydroxyquinoline)aluminum(III) (Alq₃), 2nm lithium fluoride (LiF), and 300 nm Al layers were sequentially deposited on the MoOx layer by thermal evaporation.

The intensity of visible light emission from the upconversion device was measured by a Si detector (Thorlabs DET36A). SWIR light was shine onto the upconversion imager at an incident angle of 45°. A shortpass filter (<800 nm) was placed before the Si detector to block surface-reflected SWIR light that could add unwanted contribution to the visible light measurement. The spectrum of the emitted visible light was measured by a spectrometer (Ocean Optics USB2000).

The upconversion efficiency for converting SWIR photons to visible photons is known as the photon-to-photon conversion efficiency and obtained by³⁷

$$\eta_{p-p} = \frac{N_{out}}{N_{in}} = \frac{\int I_{out}(\lambda) \lambda d\lambda}{P_{in} \lambda_{in}}, \quad (4)$$

where N_{out} is the number of visible photons emitted into the half space, N_{in} is the number of SWIR photon incident on the active area, I_{out} is the intensity of emitted visible light as a function of wavelength, and P_{in} and λ_{in} are the power and wavelength of the incident light.

Author Contributions

C.S. and N.L., and T.N.N. designed the experiments and analyzed the data. C.S. and B.S. conducted the fabrication and measurement of the devices. N.E. synthesized the SWIR polymer under the supervision of J.D.A. The principal investigator T.N.N. conceived the interlayer concept and supervised the project. All authors contributed to discussions and writing of the manuscript.

Acknowledgements

The author T. N. N. is grateful for the support from National Science Foundation award MCA-2120701. J. D. Azoulay was supported by the Air Force Office of Scientific Research under the Organic Materials Chemistry Program (FA9550-17-1-0261) and was supported by the National Science Foundation (OIA-1757220).

Conflicts of interest

The authors declare no conflict of interest.

Data Availability Statement

The data that support the findings of this study are available from the corresponding author upon reasonable request.

References

- (1) Rogalski, A. *Infrared and Terahertz Detectors, Third Edition*; CRC Press, 2019.
- (2) Wilson, R. H.; Nadeau, K. P.; Jaworski, F. B.; Tromberg, B. J.; Durkin, A. J. Review of Short-Wave Infrared Spectroscopy and Imaging Methods for Biological Tissue Characterization. *Journal of Biomedical Optics* **2015**, *20* (3), 030901.
- (3) Li, Q.; Guo, Y.; Liu, Y. Exploration of Near-Infrared Organic Photodetectors. *Chemistry of Materials* **2019**, *31* (17), 6359–6379.
- (4) Ge, Z.; Xu, N.; Zhu, Y.; Zhao, K.; Ma, Y.; Li, G.; Chen, Y. Visible to Mid-Infrared Photodetection Based on Flexible 3D Graphene/Organic Hybrid Photodetector with Ultrahigh Responsivity at Ambient Conditions. *ACS Photonics* **2022**, *9* (1), 59–67.
- (5) Li, N.; Mahalingam, P.; Vella, J. H.; Leem, D.-S. S.; Azoulay, J. D.; Ng, T. N. Solution-Processable Infrared Photodetectors: Materials, Device Physics, and Applications. *Materials Science & Engineering R-Reports* **2021**, *146* (August), 100643.
- (6) Li, N.; Eedugurala, N.; Azoulay, J. D.; Ng, T. N. A Filterless Organic Photodetector Electrically Switchable between Visible and Infrared Detection. *Cell Reports Physical Science* **2022**, *3* (1), 100711.
- (7) Strobel, N.; Seiberlich, M.; Rodlmeier, T.; Lemmer, U.; Hernandez-Sosa, G. Non-Fullerene-Based Printed Organic Photodiode with High Responsivity and Megahertz Detection Speed. *ACS Applied Materials & Interfaces* **2018**, *10* (49), 42733.
- (8) Miao, J.; Zhang, F. Recent Progress on Photomultiplication Type Organic Photodetectors. *Laser and Photonics Reviews* **2019**, *13* (2), 1800204.
- (9) Simone, G.; Dyson, M. J.; Meskers, S. C. J. J.; Janssen, R. A. J. J.; Gelinck, G. H. Organic Photodetectors and Their Application in Large Area and Flexible Image Sensors: The Role of Dark Current. *Advanced Functional Materials* **2019**, 1904205.
- (10) Wu, Z.; Li, N.; Eedugurala, N.; Azoulay, J. D.; Leem, D.-S.; Ng, T. N. Noise and Detectivity Limits in Organic Shortwave Infrared Photodiodes with Low Disorder. *npj Flexible Electronics* **2020**, *4* (1), 6.
- (11) Gielen, S.; Kaiser, C.; Verstraeten, F.; Kublitski, J.; Benduhn, J.; Spoltore, D.; Verstappen, P.; Maes, W.; Meredith, P.; Armin, A.; Vandewal, K. Intrinsic Detectivity Limits of Organic Near-Infrared Photodetectors. *Advanced Materials* **2020**, 2003818.
- (12) Kublitski, J.; Hofacker, A.; Boroujeni, B. K.; Benduhn, J.; Nikolis, V. C.; Kaiser, C.; Spoltore, D.; Kleemann, H.; Fischer, A.; Ellinger, F.; Vandewal, K.; Leo, K. Reverse Dark Current in Organic Photodetectors and the Major Role of Traps as Source of Noise. *Nature Communications* **2021**, *12* (1), 551.
- (13) Fang, Y.; Armin, A.; Meredith, P.; Huang, J. Accurate Characterization of Next-Generation Thin-Film Photodetectors. *Nature Photonics* **2019**, *13* (1), 1–4.
- (14) Wu, Y.; Fukuda, K.; Yokota, T.; Someya, T. A Highly Responsive Organic Image Sensor Based on a Two-Terminal Organic Photodetector with Photomultiplication. *Advanced Materials* **2019**, *31* (43), 1903687.
- (15) Yoon, S.; Lee, G. S.; Sim, K. M.; Kim, M. J.; Kim, Y. H.; Chung, D. S. End-Group Functionalization of Non-Fullerene Acceptors for High External Quantum Efficiency over 150 000% in Photomultiplication Type Organic Photodetectors. *Advanced Functional Materials* **2021**, *31* (1), 2006448.
- (16) Xing, S.; Kublitski, J.; Hänisch, C.; Winkler, L. C.; Li, T. yi; Kleemann, H.; Benduhn, J.; Leo, K.

- Photomultiplication-Type Organic Photodetectors for Near-Infrared Sensing with High and Bias-Independent Specific Detectivity. *Advanced Science* **2022**, *9* (7), 2105113.
- (17) Kim, J.; Kang, M.; Lee, S.; So, C.; Chung, D. S. Interfacial Electrostatic-Interaction-Enhanced Photomultiplication for Ultrahigh External Quantum Efficiency of Organic Photodiodes. *Advanced Materials* **2021**, *33* (52), 2104689.
- (18) Wu, Z.; Yao, W.; London, A. E.; Azoulay, J. D.; Ng, T. N. Elucidating the Detectivity Limits in Shortwave Infrared Organic Photodiodes. *Advanced Functional Materials* **2018**, *28* (18), 1800391.
- (19) Constantinou, I.; Yi, X.; Shewmon, N. T.; Klump, E. D.; Peng, C.; Garakyaraghi, S.; Lo, C. K.; Reynolds, J. R.; Castellano, F. N.; So, F. Effect of Polymer-Fullerene Interaction on the Dielectric Properties of the Blend. *Advanced Energy Materials* **2017**, *7*, 1601947.
- (20) Benduhn, J.; Tvingstedt, K.; Piersimoni, F.; Ullbrich, S.; Fan, Y.; Tropiano, M.; McGarry, K. A.; Zeika, O.; Riede, M. K.; Douglas, C. J.; Barlow, S.; Marder, S. R.; Neher, D.; Spoltore, D.; Vandewal, K. Intrinsic Non-Radiative Voltage Losses in Fullerene-Based Organic Solar Cells. *Nature Energy* **2017**, *2*, 17053.
- (21) Yang, K.; Wang, J.; Zhao, Z.; Sun, Y.; Liu, M.; Zhou, Z.; Zhang, X.; Zhang, F. Highly Sensitive Photomultiplication Type Polymer Photodetectors by Manipulating Interfacial Trapped Electron Density. *Chemical Engineering Journal* **2022**, *435* (P2), 134973.
- (22) Guo, D.; Yang, D.; Zhao, J.; Vadim, A.; Ma, D. Role of Interfaces in Controlling Charge Accumulation and Injection in the Photodetection Performance of Photomultiplication-Type Organic Photodetectors. *Journal of Materials Chemistry C* **2020**, *8* (26), 9024–9031.
- (23) Li, N.; Lim, J.; Azoulay, J. D.; Ng, T. N. Tuning the Charge Blocking Layer to Enhance Photomultiplication in Organic Shortwave Infrared Photodetectors. *Journal of Materials Chemistry C* **2020**, *8*, 15142–15149.
- (24) Zhao, Z.; Wang, J.; Xu, C.; Yang, K.; Zhao, F.; Wang, K.; Zhang, X.; Zhang, F. Photomultiplication Type Broad Response Organic Photodetectors with One Absorber Layer and One Multiplication Layer. *Journal of Physical Chemistry Letters* **2020**, *11* (2), 366–373.
- (25) Yaacobi-Gross, N.; Treat, N. D.; Pattanasattayavong, P.; Faber, H.; Perumal, A. K.; Stingelin, N.; Bradley, D. D. C.; Stavrinou, P. N.; Heeney, M.; Anthopoulos, T. D. High-Efficiency Organic Photovoltaic Cells Based on the Solution-Processable Hole Transporting Interlayer Copper Thiocyanate (CuSCN) as a Replacement for PEDOT:PSS. *Advanced Energy Materials* **2015**, *5* (3), 1401529.
- (26) Huang, J.; Lee, J.; Nakayama, H.; Schrock, M.; Cao, D. X.; Cho, K.; Bazan, G. C.; Nguyen, T. Q. Understanding and Countering Illumination-Sensitive Dark Current: Toward Organic Photodetectors with Reliable High Detectivity. *ACS Nano* **2021**, *15* (1), 1753–1763.
- (27) Liang, J.; Chen, Z.; Yang, G.; Wang, H.; Ye, F.; Tao, C.; Fang, G. Achieving High Open-Circuit Voltage on Planar Perovskite Solar Cells via Chlorine-Doped Tin Oxide Electron Transport Layers. *ACS Applied Materials and Interfaces* **2019**, *11* (26), 23152–23159.
- (28) Jiang, Y.; Sun, L.; Jiang, F.; Xie, C.; Hu, L.; Dong, X.; Qin, F.; Liu, T.; Hu, L.; Jiang, X.; Zhou, Y. Photocatalytic Effect of ZnO on the Stability of Nonfullerene Acceptors and Its Mitigation by SnO₂ for Nonfullerene Organic Solar Cells. *Materials Horizons* **2019**, *6* (7), 1438–1443.
- (29) Mohamad Noh, M. F.; Teh, C. H.; Daik, R.; Lim, E. L.; Yap, C. C.; Ibrahim, M. A.; Ahmad Ludin, N.; Mohd Yusoff, A. R. Bin; Jang, J.; Mat Teridi, M. A. The Architecture of the

- Electron Transport Layer for a Perovskite Solar Cell. *Journal of Materials Chemistry C* **2018**, *6* (4), 682–712.
- (30) Xiong, L.; Guo, Y.; Wen, J.; Liu, H.; Yang, G.; Qin, P.; Fang, G. Review on the Application of SnO₂ in Perovskite Solar Cells. *Advanced Functional Materials* **2018**, *28* (35), 1802757.
- (31) Jiang, Q.; Zhang, X.; You, J. SnO₂: A Wonderful Electron Transport Layer for Perovskite Solar Cells. *Small* **2018**, *14* (31), 1801154.
- (32) Xiong, C.; Yao, R. H.; Wan, W. J.; Xu, J. X. Fabrication and Electrical Characterization of ZnO Rod Arrays/CuSCN Heterojunctions. *Optik* **2014**, *125* (2), 785–788.
- (33) Kim, H.; Wu, Z.; Eedugurala, N.; Azoulay, J. D.; Ng, T. N. Solution-Processed Phototransistors Combining Organic Absorber and Charge Transporting Oxide for Visible to Infrared Light Detection. *ACS Applied Materials and Interfaces* **2019**, *11* (40), 36880–36885.
- (34) Rim, Y. S.; Ok, K. C.; Yang, Y. M.; Chen, H.; Bae, S. H.; Wang, C.; Huang, Y.; Park, J. S.; Yang, Y. Boosting Responsivity of Organic-Metal Oxynitride Hybrid Heterointerface Phototransistor. *ACS Applied Materials and Interfaces* **2016**, *8* (23), 14665–14670.
- (35) Furchi, M. M.; Polyushkin, D. K.; Pospischil, A.; Mueller, T. Mechanisms of Photoconductivity in Atomically Thin MoS₂. *Nano Lett* **2014**, *14* (11), 6165–6170.
- (36) Pierre, A.; Gaikwad, A.; Arias, A. C. Charge-Integrating Organic Heterojunction Phototransistors for Wide-Dynamic-Range Image Sensors. *Nature Photonics* **2017**, *11* (3), 193–199.
- (37) Hany, R.; Cremona, M.; Strassel, K. Recent Advances with Optical Upconverters Made from All-Organic and Hybrid Materials. *Science and Technology of Advanced Materials* **2019**, *20* (1), 497–510.
- (38) Song, Q.; Lin, T.; Su, Z.; Chu, B.; Yang, H.; Li, W.; Lee, C. S. Organic Upconversion Display with an over 100% Photon-to-Photon Upconversion Efficiency and a Simple Pixelless Device Structure. *Journal of Physical Chemistry Letters* **2018**, *9* (23), 6818–6824.
- (39) Li, N.; Eedugurala, N.; Leem, D. S.; Azoulay, J. D.; Ng, T. N. Organic Upconversion Imager with Dual Electronic and Optical Readouts for Shortwave Infrared Light Detection. *Advanced Functional Materials* **2021**, 2100565.
- (40) Yang, D.; Zhou, X.; Ma, D.; Vadim, A.; Ahamad, T.; Alshehri, S. M. Near Infrared to Visible Light Organic Up-Conversion Devices with Photon-to-Photon Conversion Efficiency Approaching 30%. *Materials Horizons* **2018**, *5* (5), 874–882.
- (41) Ren, H.; Chen, J.-D.; Li, Y.-Q.; Tang, J.-X. Recent Progress in Organic Photodetectors and Their Applications. *Advanced Science* **2021**, *8* (1), 2002418.
- (42) Zhou, W.; Shang, Y.; García de Arquer, F. P.; Xu, K.; Wang, R.; Luo, S.; Xiao, X.; Zhou, X.; Huang, R.; Sargent, E. H.; Ning, Z.; Arquer, F. P. G. De; Xu, K.; Wang, R.; Luo, S.; Xiao, X.; Zhou, X.; Huang, R.; Sargent, E. H.; Ning, Z. Solution-Processed Upconversion Photodetectors Based on Quantum Dots. *Nature Electronics* **2020**, *3* (5), 251–258.
- (43) Wu, Z.; Zhai, Y.; Yao, W.; Eedugurala, N.; Zhang, S.; Huang, L.; Gu, X.; Azoulay, J. D.; Ng, T. N. The Role of Dielectric Screening in Organic Shortwave Infrared Photodiodes for Spectroscopic Image Sensing. *Advanced Functional Materials* **2018**, *28* (50), 1805738.
- (44) Vella, J. H.; Huang, L.; Eedugurala, N.; Mayer, K.; Ng, T. N.; Azoulay, J. Broadband Infrared Photodetection Using a Narrow Bandgap Conjugated Polymer. *Science Advances* **2021**, abg2418.

- (45) Tran, V. H.; Khan, R.; Lee, I. H.; Lee, S. H. Low-Temperature Solution-Processed Ionic Liquid Modified SnO₂ as an Excellent Electron Transport Layer for Inverted Organic Solar Cells. *Solar Energy Materials and Solar Cells* **2018**, *179* (September 2017), 260–269.