



Cite this: *Green Chem.*, 2020, **22**, 6062

## Using iron sulphate to form both n-type and p-type *pseudo*-thermoelectrics: non-hazardous and 'second life' thermogalvanic cells†

Mark A. Buckingham,  Kristine Laws,  Jason T. Sengel and Leigh Aldous \*

Thermogalvanic cells can act like 'liquid thermoelectrics' to convert a thermal energy gradient to electrical energy. Such cells are typically combined electrically in-series in devices to boost the output voltage (as thermocells). However, the typical system involves a potentially fatal combination of inherently acidic or acidified  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  electrolytes; mixing and heating is expected to trigger extremely toxic HCN gas release. Here we demonstrate that benign aqueous iron(II/III) sulphate can be combined with equally benign sodium sulphate and sodium hydrogen sulphate; the first leads to an  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  thermocell (Seebeck coefficient,  $S_e = -0.4 \text{ mV K}^{-1}$ ), and the second to a thermocell with intermediate  $[\text{FeSO}_4]^{0/+}$  and  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  character ( $S_e = +0.57 \text{ mV K}^{-1}$ ). Their fundamental thermoelectrochemistry was explored, and their speciation elucidated. It was demonstrated that these can be utilised electrically in-parallel and in-series in thermogalvanic devices. When connected electrically in-series the thermocells presented here displayed temperature-dependent open circuit potentials only *ca.* one-third that typically reported for the 'conventional' combination of  $\text{Fe}^{2+/3+}$ - and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$ -based thermocells ( $0.8 \text{ mV K}^{-1}$  vs. *ca.*  $3 \text{ mV K}^{-1}$ , respectively). However, whereas the latter thermocells cannot be safely mixed, when the iron-sulphate cells were 'accidentally' mixed they safely form a mixed thermocell electrolyte ( $S_e = +0.19 \text{ mV K}^{-1}$ ), enabling a 'second life' of both the electrolyte and thermocell devices. This novel 'all-iron sulphate' thermocell was compared against the typically employed  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  combination using the 12 principles of green chemistry and of green engineering, further demonstrating the inherent sustainability, safety and 'green' credentials of this system (but not yet efficiency). This work demonstrates how functionality and complexity can be introduced in a safe manner, while also preventing potential accidents and enabling new 'end-of-life' opportunities.

Received 2nd June 2020,  
Accepted 18th August 2020  
DOI: 10.1039/d0gc01878c

rsc.li/greenchem

## Introduction

Both solid-state thermoelectric systems and liquid-state thermogalvanic systems exploit entropy; when exposed to a temperature difference across these systems they generate a flow of electricity.<sup>1</sup> Given that approximately two-thirds of the energy deliberately generated by mankind is currently lost as heat,<sup>2</sup> such devices present tremendous potential for improving global energy efficiency.

The magnitude of potential difference generated by these systems is typically quantified by the Seebeck coefficient,  $S_e$ .<sup>3</sup> For thermoelectrics, this is given by eqn (1),<sup>3</sup>

$$\frac{\Delta V}{\Delta T} = -S_{e(\text{te})} \quad (1)$$

where  $\Delta V$  is the potential difference generated when exposed to a temperature difference,  $\Delta T$ , giving the thermoelectric Seebeck coefficient,  $S_{e(\text{te})}$ . The sign of the  $S_e$  shows the direction of current flow with respect to the temperature difference.<sup>3,4</sup> A typical thermoelectric device requires two types of thermoelectric materials: one with a positive  $S_{e(\text{te})}$  (electrons move from hot to cold; n-type conductor), the other with a negative  $S_{e(\text{te})}$  (holes move from hot to cold; p-type).<sup>5,6</sup> These are connected electrically in-series to boost the potential output, while ensuring the electrical connection is thermally in-parallel (to prevent a thermal short circuit across the device).<sup>4,5</sup> Taking  $S_{e(\text{te})}$  values on the order of  $350 \mu\text{V K}^{-1}$  (typical of  $\text{Bi}_2\text{Te}_3$  devices<sup>5</sup>), such a thermoelectric device would require *ca.* 285 pairs of n-p thermoelectrics in-series to generate 1 V at  $\Delta T = 10 \text{ K}$ . Such semiconductor devices are also typically composed of rare and toxic elements such as bismuth, lead, tin, selenium, silver, indium, gallium, germanium and tellurium;<sup>7</sup> based upon current usage, all are classified as 'endangered elements' and face future supply limitations, with

Department of Chemistry, Britannia House, King's College London, London, SE1 1DB, UK. E-mail: leigh.aldous@kcl.ac.uk

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0gc01878c



the latter five classified as facing serious threat of exhaustion and dissipation in the next 100 years.<sup>8</sup>

Thermogalvanic devices can be considered as *pseudo*-thermoelectric devices, although their precise mechanism of operation differs significantly. Thermogalvanics are typically liquid-state or gelled-liquid electrolyte devices.<sup>9</sup> These electrolytes contain two oxidation states of a common redox couple, sandwiched between two electrodes at dissimilar temperatures; ionic conductivity replaces electron and hole transport.<sup>10</sup> The thermogalvanic Seebeck coefficient,  $S_{e(\text{tg})}$ , is related to the entropy difference between the two states of the redox couple,  $\Delta S_{\text{rc}}$ , as shown by eqn (2);

$$\frac{\Delta V}{\Delta T} = S_{e(\text{tg})} = -\frac{\Delta S_{\text{rc}}}{nF} \quad (2)$$

where  $n$  is the number of electrons, and  $F$  the Faraday constant.<sup>11</sup> Early conventions diverged in the 1970–80s<sup>10,11</sup> which has resulted in the majority of reported  $S_{e(\text{tg})}$  values having the opposite sign to the  $S_{e(\text{te})}$  (note the different signs in eqn (1) and (2)); eqn (2) matches the IUPAC conventions on the temperature coefficient of the standard electrode potentials,<sup>12</sup> and is the convention adopted here. A positive  $S_{e(\text{tg})}$  therefore indicates the hotter electrode behaves as the cathode (reduction occurs), and the direction of current flow matches an n-type thermoelectric.<sup>13</sup> Taking  $S_{e(\text{tg})}$  values on the order of  $\pm 1.5 \text{ mV K}^{-1}$  for typical thermogalvanic systems,<sup>4,14–17</sup> this means only *ca.* 33 pairs are required to generate 1 V at a 10 K temperature difference. Therefore, significantly fewer pairs are required when compared to thermoelectric devices, but such electrical combinations are still essential in order to generate appreciable potential outputs from thermogalvanic devices.

Several n–p-type thermogalvanic combinations (one  $+S_{e(\text{tg})}$ , one  $-S_{e(\text{tg})}$ ) have been reported, but not applied to prepare complete devices that generate a consistent power output. For example, Jia *et al.* observed different ratios of water to ionic liquid in binary systems could yield either positive or negative  $S_{e(\text{tg})}$  values;<sup>18</sup> Liang *et al.* observed different ratios of  $[\text{S}_3]^{2-}$  to  $\text{S}_8$  in DMSO could also result in different  $S_{e(\text{tg})}$  signs.<sup>19</sup> Aldous *et al.* demonstrated how the ferrocene/ferrocenium redox couple could be made to have a positive or negative  $S_{e(\text{tg})}$  in ionic liquids by covalently tethering on appropriately charged groups.<sup>20</sup>

For actual devices (or thermocells) with multiple thermogalvanic cells in-series to boost the voltage output, one device was recently reported where the  $S_{e(\text{tg})}$  of the aqueous  $\text{I}^-/[\text{I}_3]^-$  redox couple ( $+0.71 \text{ mV K}^{-1}$ ) was inverted into the p-type direction upon introduction of poly-*N*-isopropylacrylamide, to  $-1.91 \text{ mV K}^{-1}$ .<sup>21</sup> Using this, 50 n–p-type pairs were combined to form a device capable of generating 1 V from body heat.<sup>21</sup> Besides this, other reported thermocell devices employ inherently or deliberately acidified aqueous solutions of  $\text{Fe}^{2+/3+}$  ( $S_{e(\text{tg})}$  up to  $+1.76 \text{ mV K}^{-1}$ ) in conjunction with aqueous solutions of  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  ( $S_{e(\text{tg})}$  up to  $-1.43 \text{ mV K}^{-1}$ ).<sup>4,14–17</sup> Fundamental studies have recently probed the  $\text{Fe}^{2+/3+}$  system<sup>22</sup> and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  system<sup>23</sup> in detail, as well as the fundamentals of their combinations electrically in-series and in-parallel.<sup>4</sup>

These in-series thermocell devices have also been applied, *e.g.* to charge capacitors<sup>15,17</sup> and light LEDs.<sup>16</sup>

One major drawback of the combined usage of inherently acidic  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  in a thermocell device is their mutual incompatibility. Both  $[\text{Fe}(\text{CN})_6]^{3-}$  and  $[\text{Fe}(\text{CN})_6]^{4-}$  are unstable when exposed to UV light,<sup>24–26</sup> normal tungsten or fluorescent lighting,<sup>27</sup> high pH,<sup>24</sup> low pH<sup>28,29</sup> and high temperatures.<sup>30–33</sup> In particular, the degradation products at high temperature and low pH is known to be  $\text{HCN}$ <sup>28,30,31,34</sup> which is extremely toxic to humans.<sup>35–37</sup> Thermocell  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  electrolytes even dissolve gold nanoparticles, *via*  $\text{CN}^-$  loss.<sup>38</sup>

Risk assessment prior to preparing such thermocells revealed that neither  $\text{K}_3[\text{Fe}(\text{CN})_6]$  nor  $\text{K}_4[\text{Fe}(\text{CN})_6]$  should be combined with acid and heated;<sup>39,40</sup> there is even a tragic suicide case where  $\text{K}_4[\text{Fe}(\text{CN})_6]$  was heated with acid in a sealed vehicle environment to release a lethal dose of  $\text{HCN}$ .<sup>36</sup> Despite this, reported thermocell works note using  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  solutions in close conjunction with a heat source and  $\text{Fe}^{2+/3+}$  solutions containing up to 10 wt%  $\text{HCl}$ ,<sup>17</sup> and even non-acidified aqueous solutions of  $\text{Fe}^{2+/3+}$  are strongly inherently acidic due to water-of-hydration hydrolysis.<sup>22</sup> Table 1 summarises five reported works which used  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  to prepare in-series thermocell devices; the produced electrical power values are reported, but for each a ‘worst case scenario’ is also explored, based upon the electrolytes in the reported devices accidentally mixing. It was assumed that the  $[\text{Fe}(\text{CN})_6]^{4-}$  evolved  $\text{HCN}_{(\text{g})}$ , and the resulting  $\text{HCN}_{(\text{g})}$  concentration was calculated for five sealed-environment scenarios. While  $[\text{Fe}(\text{CN})_6]^{3-}$  is also known to decompose, it typically decomposes significantly more slowly; accounting for  $[\text{Fe}(\text{CN})_6]^{3-}$  would double the  $\text{HCN}$  evolution values in Table 1. The colour coding in Table 1 indicates likely human outcomes based upon AEGL toxicity levels,<sup>41</sup> with red being lethal or life-threatening, orange indicating likely irreversible health effects, yellow likely causing discomfort, and green likely no effect.

What is clear from Table 1 is that as these devices evolve and become bigger, more concentrated and more powerful (*cf.* the maximum power column), the inherent risk inevitably increases; even if the worst case scenarios are not realised, partial  $\text{HCN}_{(\text{g})}$  evolution still pose major risks in confined environments. To this end, we demonstrate here how a single chemical source can be combined with relatively benign additives to generate thermogalvanic cells with both positive and negative  $S_{e(\text{tg})}$  values, allowing their electrical combination in-series and in-parallel, as is common in n–p-type thermoelectric devices. This was based upon an aqueous mixture of iron (ii) and iron(III) sulphate with sodium sulphate or sodium hydrogen sulphate as additives. These simple additives were used to increase or decrease the degree of complexation of the metal centre with the sulphate dianion. Ultimately, in-series and in-parallel thermocell devices were prepared, and mixing of the electrolytes managed to retain thermogalvanic activity, thus leading to a ‘second life’ thermocell, making it safe and ‘unbreakable’, relative to the widely reported  $\text{Fe}^{2+/3+} +$



**Table 1** Demonstrates the published thermocell devices using multiple  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  cells, and how as they increase in maximum power output the potential hazard of HCN gas evolution also increases. A 'worst case scenario' was assumed, *i.e.* that the electrolytes mixed and all of the  $[\text{Fe}(\text{CN})_6]^{4-}$  present completely decomposed to evolve  $6\text{HCN}_{(\text{g})}$  (full calculations detailed in the ESI†). The  $[\text{Fe}(\text{CN})_6]^{3-}$  is relatively more stable, so was not included, but can be included by doubling values. The resulting concentration in ppm ( $\text{mg m}^{-3}$ ) was estimated for 5 different volumes. These were then colour-coded based upon the AEG<sup>41</sup> exposure limit for  $\text{HCN}_{(\text{g})}$ , where  $>6.5 \text{ mg m}^{-3}$  = life-threatening or death (red);  $2.5\text{--}6.5$  = irreversible and long-lasting health effects (orange);  $1\text{--}2.4$  = discomforting but non-disabling (yellow); and  $<1$  = non-toxic (green), based upon exposure times of 8 hours. The thermocell reported by Lee *et al.* is the most recently reported, and most powerful to date, being able to light LEDs<sup>16</sup>

Corresponding author	$S_c$ for n- & p-type/ $\text{mV K}^{-1}$	Max. power <sup>a</sup> / $\mu\text{W}$	HCN in $\text{mg m}^{-3}$ (assuming HCN-evolution, within the defined volume)				
			Cubic meter: $1 \text{ m}^3$	Car <sup>b</sup> : $3.5 \text{ m}^3$	Conference room <sup>c</sup> : $71 \text{ m}^3$	Flat <sup>d</sup> : $137 \text{ m}^3$	Airplane <sup>e</sup> : $295 \text{ m}^3$
Zhou <sup>17</sup>	+1.02/−1.21	0.3	6.8	1.9	0.10	0.05	0.02
Kang <sup>14</sup>	+1.76/−1.26	0.9	8.4	2.4	0.12	0.06	0.03
Aldous <sup>4</sup>	+0.54/−0.95	5.4	16.3	4.7	0.23	0.12	0.06
Baughman <sup>15</sup>	+0.50/−1.43	—	472.2	134.9	6.65	3.4	1.6
Lee <sup>16</sup>	+1.74/−1.29	2500	2185.5	624.4	30.78	16.0	7.4

<sup>a</sup> See Table S1† for full details. <sup>b</sup> Medium-sized car, USA: <https://www.fueleconomy.gov/feg/info.shtml#sizeclasses>. <sup>c</sup> Typical conference room for 80 delegates: <https://www.meetings.com/Meeting-Room-Capacity-Calculator>. <sup>d</sup> Typical UK flat size, calculated from the typical floor plan area, and assuming a typical room height of 2.4 m: [https://www.savills.co.uk/research\\_articles/229130/188035-0](https://www.savills.co.uk/research_articles/229130/188035-0). <sup>e</sup> Total interior volume of Airbus A320, estimated using the airplane fuselage length and width: <https://www.airbus.com/aircraft/passenger-aircraft/a320-family/a320neo.html#details>.

$[\text{Fe}(\text{CN})_6]^{3-/4-}$  analogues. Qualitative comparisons *vs.* the principles of green chemistry and green engineering further confirmed this.

## Experimental

### Chemicals

All reagents were purchased from UK suppliers and were used as received, unless otherwise specified. These were iron(II) sulphate heptahydrate (99%, Acros Organics), iron(III) sulphate (97% Acros Organics), sodium sulphate (98%, Sigma Aldrich), potassium carbonate (Santa Cruz Biotechnology) and sodium hydrogen sulphate (Sigma Aldrich).

### Thermogalvanic measurements

All thermoelectrochemical measurements were performed using two types of tailor-made poly(methyl methacrylate) (PMMA) cells, which were made in-house; a two-chamber thermocell and a six-chamber thermocell. The two-chamber thermocell was machined from a single block of PMMA (30 mm (width)  $\times$  20 mm (height)  $\times$  8.4 mm (depth)) and has been previously reported in detail elsewhere.<sup>23</sup> The six-chamber thermocell was machined from a larger block (30 mm (width)  $\times$  44 mm (height)  $\times$  8.4 mm (depth)). Each chamber was a 6.7 mm diameter cylinder (giving a geometric electrode surface area of  $35 \text{ mm}^2$ ) and giving an inter-electrode spacing of 7.4 mm. The electrodes were 10 mm diameter circles which were inserted into 0.5 mm deep lips machined around the chambers in the thermocell, and were either solid gold electrodes (1 mm thick discs with 10 mm diameter, from Surepure Chemetals, USA) or previously characterised amorphous graphite<sup>23</sup> (cut into circles by hand).

Temperature control was achieved using copper heat exchangers connected to RS-TX150 thermostatic circulator baths (Grant Instruments Ltd, UK), as previously described.<sup>23</sup>

Notably, some temperature gradients form between the isothermal water sources and the surfaces of the thermogalvanic electrode; this has been previously characterised for our cell,<sup>42</sup> such that an applied temperature difference,  $\Delta T$ , of 20 K, equates to an 'experienced' temperature difference of *ca.* 18 K. The applied (rather than experienced) temperature difference is utilised throughout this manuscript, unless explicitly stated (*cf.* Table S2, ESI†).

All potential, current and power measurements were performed using a Keysight B2901A Source Measure Unit and Quick IV software (Keysight, UK), were carefully measured and allowed to reach steady-state, following precisely the 'sequence of constant voltages' method previously reported.<sup>42</sup>

### Cyclic voltammetry

Cyclic voltammetric experiments were carried out using a PGSTAT204 potentiostat with NOVA software (Metrohm, UK). The electrochemical setup was a 1.6 mm diameter Au disc working electrode, a 1.6 mm diameter Pt disc counter electrode, and an Ag/AgCl (3 M NaCl) reference electrode (all BASi, USA). All scans were recorded at a scan rate of  $100 \text{ mV s}^{-1}$ , unless specified otherwise (Fig. S5 in the ESI† demonstrates a scan rate study of the investigated systems). The cyclic voltammetry was performed *ex situ* in an isothermal setup.

### Electrochemical impedance spectroscopy

Electrochemical impedance spectroscopy measurements were carried out using a PGSTAT204 potentiostat with NOVA software (Metrohm, UK). These were performed *in situ* inside the thermocell at non-isothermal temperatures, using  $\Delta T = 20 \text{ K}$  ( $T_h = 40 \text{ }^\circ\text{C}$ ;  $T_c = 20 \text{ }^\circ\text{C}$ ). Impedance was performed on both gold and graphite electrodes. Typically, the hot electrode was employed as the working electrode and the cold electrode employed as the counter electrode, unless otherwise specified (*cf.* Fig. S6†).



## UV-Vis and IR spectroscopy

All spectra were obtained using solutions containing either 0.03 M of the Fe(II) sulphate or 0.03 M of the Fe(III) sulphate, in the presence or absence of 0.075 M of either NaHSO<sub>4</sub> or Na<sub>2</sub>SO<sub>4</sub>. UV-Vis spectroscopy was performed using a Cary 100 UV-Vis and WinUV software (Agilent, UK) between 200–800 nm and with a UV-Vis crossover wavelength of 400 nm, at ambient temperature (*ca.* 20 °C), using quartz cuvettes with a path length of 100 μm (FireflySci, USA). IR spectroscopy was performed on the same solutions, using a droplet placed on a monolithic diamond ATR (Quest ATR Diamond accessory, Specac Ltd, UK) connected to an IRAffinity-1S Shimadzu spectrophotometer (Shimadzu, UK); results were obtained over 32 scans with a resolution of 4 cm<sup>-1</sup>.



## Results and discussion

### Seebeck coefficient sign inversion in the iron sulphate system


Initially a stoichiometric aqueous mixture of iron(II) and iron(III) sulphate (0.3 M of each) was investigated. This mixture (abbreviated as [Fe(SO<sub>4</sub>)]) yielded an apparent Seebeck coefficient (*aS<sub>e</sub>*) of +0.27 mV K<sup>-1</sup> (shown in Fig. 1; blue circle in top left). This is slightly lower than previously reported values, with three similar un-acidified solutions also reporting *S<sub>e</sub>* in

the range of +0.29 to +0.34 mV K<sup>-1</sup>.<sup>4,16,22</sup> This is likely due to this study using a higher concentration of [Fe(SO<sub>4</sub>)] (which will reduce the *S<sub>e</sub>*) and also due to not correcting the applied temperature difference to the experienced temperature difference (explained in the Experimental section). The values measured here are referred to as the ‘apparent Seebeck coefficient’ (*aS<sub>e</sub>*) because they are only valid for the precise temperatures used (*T<sub>c</sub>*, *T<sub>h</sub>* and  $\Delta T$ ; explained in more detail below).

Next, acidification of the solution was explored. Acidified solutions of [Fe(SO<sub>4</sub>)] have previously been used in thermogalvanic cells.<sup>4,15,16,22</sup> Specifically the addition of H<sub>2</sub>SO<sub>4</sub> to [Fe(SO<sub>4</sub>)] thermocell solutions significantly increases the *S<sub>e</sub>* (with reported values between +0.50 and +0.90 mV K<sup>-1</sup>, depending upon concentration and pH),<sup>4,15,22</sup> although notably this is below the *S<sub>e</sub>* observed for un-acidified hexaaqua Fe<sup>2+/3+</sup> solutions (between 1.35 and 1.66 mV K<sup>-1</sup>).<sup>16,22</sup> The *S<sub>e</sub>* observed for hexaaqua Fe<sup>2+/3+</sup> solutions are also slightly increased by acidification.<sup>22</sup> These observations have been attributed to the hexaaqua species being partially susceptible to hydrolysis (exemplified by Fe<sup>3+</sup> in eqn (3)), whereas the un-acidified [Fe(SO<sub>4</sub>)] solutions demonstrate association of the Fe<sup>3+</sup> with the sulphate dianion (eqn (4));<sup>16,22</sup> this reduces the charge of the complex and hence lowers the *S<sub>e</sub>*.<sup>43</sup>



Acidification of the hexaaqua species shifts eqn (3) to the left, whereas acidification of [Fe(SO<sub>4</sub>)] with H<sub>2</sub>SO<sub>4</sub> is speculated to protonate the sulphate dianion (eqn (5)),<sup>22</sup> increasing the fixed charge on the complex, and thus increasing the apparent *S<sub>e</sub>*.

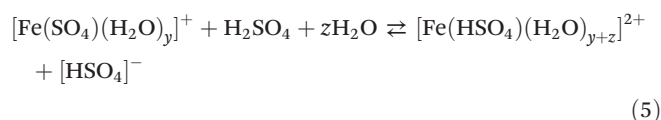

Since H<sub>2</sub>SO<sub>4</sub> is highly corrosive and ecologically damaging if released into the environment,<sup>44</sup> the significantly more benign alternative sodium hydrogen sulphate (NaHSO<sub>4</sub>) was explored. Notably, sodium (Na<sup>+</sup>), hydrogen sulphate ([HSO<sub>4</sub>]<sup>-</sup>) and sulphate ([SO<sub>4</sub>]<sup>2-</sup>) ions are all naturally abundant in water sources, including tap water.<sup>22</sup> As shown in Fig. 1, addition of 1.5 M NaHSO<sub>4</sub> to the [Fe(SO<sub>4</sub>)] system increased the *aS<sub>e</sub>* from +0.27 mV K<sup>-1</sup> to +0.50 mV K<sup>-1</sup> (Fig. 1, red square). A concentration study demonstrated *aS<sub>e</sub>* increased with increasing NaHSO<sub>4</sub> concentration (Fig. S1(d)†). While this change is not as significant as that achieved by the addition of 1 M H<sub>2</sub>SO<sub>4</sub> (previously reaching up to +0.9 mV K<sup>-1</sup>)<sup>22</sup> it nevertheless demonstrates a new and less potentially hazardous route of enhancing the positive *S<sub>e</sub>* of the [Fe(SO<sub>4</sub>)] system.


Next, the effect of Na<sub>2</sub>SO<sub>4</sub> addition was evaluated. As shown by the trend in Fig. 1, increasing concentrations of Na<sub>2</sub>SO<sub>4</sub> in the [Fe(SO<sub>4</sub>)] system resulted in a decrease in the *aS<sub>e</sub>*, so much so that the system switched from a positive *aS<sub>e</sub>* to a negative *aS<sub>e</sub>*. The solubility limit of the system was reached by 1.5 M



Fig. 1 Plot of the potential difference ( $\Delta V$ ) generated and corresponding apparent Seebeck coefficient (*aS<sub>e</sub>*) when the thermocell was exposed to a temperature difference ( $\Delta T$ ) of 20 K. All systems contained 0.3 M Fe(II) and 0.3 M Fe(III) sulphate, with various Na<sub>2</sub>SO<sub>4</sub> concentrations from 0 M to 1.5 M (as indicated by the x-axis), which resulted in inversion from a positive *aS<sub>e</sub>* (equivalent to an n-type thermoelectric) to negative *aS<sub>e</sub>* (p-type thermoelectric). Systems also containing either 1.5 M NaHSO<sub>4</sub> or 25 mM K<sub>2</sub>CO<sub>3</sub> are indicated. The temperature applied to the colder electrode, *T<sub>c</sub>*, was fixed at 20 °C. All values are the average of triplicate measurements; error bars ( $\pm 1$  standard deviation) were smaller than the size of the data point and so are not shown. The effect of iron sulphate concentration and NaHSO<sub>4</sub> concentration are shown in Fig. S1.†



Na<sub>2</sub>SO<sub>4</sub>, which gave an aS<sub>e</sub> of −0.29 mV K<sup>−1</sup> (shown in Fig. 1; blue circle in bottom right). This inversion in aS<sub>e</sub> implies that the reduced species, Fe(II), now possesses a larger effective ionic charge than the oxidised species, Fe(III), such that reduction of Fe(III) to Fe(II) now occurs at the colder electrode in the thermocell. This is consistent with coordination of the iron cations with at least two [SO<sub>4</sub>]<sup>2−</sup> groups, as shown in eqn (6) and (7) for Fe(II) and Fe(III), respectively (water of hydration omitted for clarity).



Whereas the positive aS<sub>e</sub> systems became more positive upon acidification, the negative aS<sub>e</sub> systems also became more negative upon addition of base, e.g. the addition of 25 mM K<sub>2</sub>CO<sub>3</sub> increased the aS<sub>e</sub> coefficient (Fig. 1, green triangle) from −0.26 to −0.31 mV K<sup>−1</sup>. This is likely due to removal of some [HSO<sub>4</sub>]<sup>−</sup> present in the system, and thus further increasing the concentration of [SO<sub>4</sub>]<sup>2−</sup>. However, iron is known to have a rich, pH-dependent chemistry,<sup>45,46</sup> and Fe(III) precipitates ≥pH 2.5.<sup>47</sup> In this study, further addition beyond 1.5 M Na<sub>2</sub>SO<sub>4</sub> and 25 mM K<sub>2</sub>CO<sub>3</sub> resulted in rapid precipitation of the system.

The above observations are significant because they demonstrate that the Fe<sup>2+/3+</sup> redox couple can be used as their relatively inexpensive and innocuous sulphate salts, and as-dissolved they yield a system roughly equivalent to [Fe(SO<sub>4</sub>)]<sup>0/+</sup> (aS<sub>e</sub> = +0.27 mV K<sup>−1</sup>). Minor acidification with 1.5 M NaHSO<sub>4</sub> increases the [Fe(HSO<sub>4</sub>)]<sup>+2+</sup> character of the system (aS<sub>e</sub> = +0.50 mV K<sup>−1</sup>), whereas the presence of 1.5 M Na<sub>2</sub>SO<sub>4</sub> inverts the redox chemistry to give behaviour consistent with [Fe(SO<sub>4</sub>)<sub>2</sub>]<sup>−/2−</sup> (aS<sub>e</sub> = −0.29 mV K<sup>−1</sup>). Thus, if these systems can thermogalvanically generate electricity they could be used to prepare ‘all-iron sulfate in-series’ thermocells. Their ability to do this was therefore investigated.

## Thermogalvanic current and power properties of the iron sulphate systems

The same systems explored in Fig. 1 were measured thermogalvanically, and their current and power output quantified. The short circuit current density (*j*<sub>SC</sub>) produced by a single thermogalvanic cell (Fig. 2(a)) had the same trend as the aS<sub>e</sub> (cf. Fig. 1); this makes sense since the aS<sub>e</sub> is a major driving force in the current produced, as expressed by the Butler–Volmer equation.<sup>23</sup> The maximum electrical power produced, *P*<sub>max</sub>, is given by *P*<sub>max</sub> = 0.25 × aS<sub>e</sub> × *j*<sub>SC</sub>, and the investigated systems displayed a clear U-like trend (Fig. 2(b)); maximum power was produced at the extremes of the system, namely those with the largest absolute aS<sub>e</sub> values, which in turn generated the larger absolute *j*<sub>SC</sub> values and thus even larger *P*<sub>max</sub> values. These results clearly demonstrate the various systems are able to generate electrical power *via* the thermogalvanic effect, but the direction and magnitude of the current flow is strongly influenced by the concentration of [SO<sub>4</sub>]<sup>2−</sup> and [HSO<sub>4</sub>]<sup>−</sup>.

## Temperature dependence of the thermoelectrochemistry

The thermogalvanic Seebeck coefficient for a system at a given concentration is generally a temperature-independent constant, which is unaffected by the temperature of the hotter electrode, the colder electrode and the temperature difference<sup>1</sup> (within reason). However, this does not apply if there are temperature-dependent equilibria present in the system.<sup>22,48</sup>

Throughout the rest of this study, three systems were exclusively investigated: one containing 0.3 M Fe(II)[SO<sub>4</sub>] and 0.3 M Fe(III)[SO<sub>4</sub>]<sub>1.5</sub> (the [Fe(SO<sub>4</sub>)]<sup>0/+</sup> system), and another two based upon this but in addition containing 1.5 M NaHSO<sub>4</sub> ([Fe(HSO<sub>4</sub>)]<sup>+2+</sup>) or 1.5 M Na<sub>2</sub>SO<sub>4</sub> ([Fe(SO<sub>4</sub>)<sub>2</sub>]<sup>−/2−</sup>), respectively. Systems containing K<sub>2</sub>CO<sub>3</sub> were not explored further, given the additional complexity it introduced for only minor benefit. The thermogalvanic Seebeck coefficients for all three systems were measured under a range of conditions, and all three were found to be temperature sensitive; in particular, they were found to be most influenced by the temperature of the colder electrode, *T*<sub>c</sub>. Fig. 3 displays the measured apparent

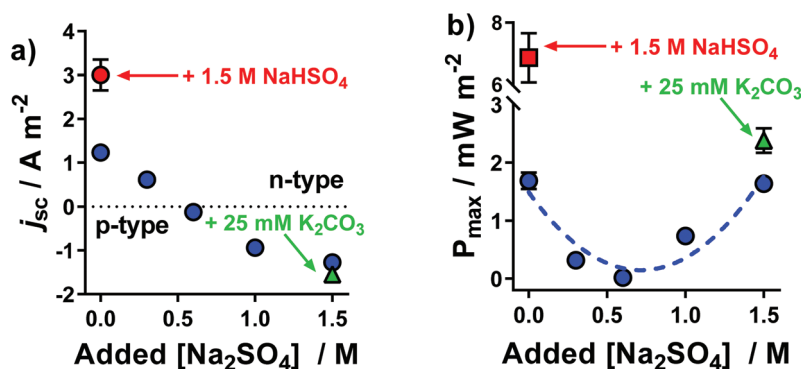


Fig. 2 Plots of the (a) short-circuit current density, *j*<sub>SC</sub>, and (b) maximum power density, *P*<sub>max</sub>, generated by the thermocells as a function of Na<sub>2</sub>SO<sub>4</sub> concentration; all experimental conditions are the same as Fig. 1. All values are the average of triplicate measurements; error bars represent ±1 standard deviation, and no error bars indicate error was equal to or smaller than the size of the data point. The effect of iron sulphate concentration and NaHSO<sub>4</sub> concentration are shown in Fig. S1.†





**Fig. 3** Plot of the  $aS_e$  measured at four different  $\Delta T$  values for 0.3 M Fe(II) and 0.3 M Fe(III) sulphate ( $[\text{Fe}(\text{SO}_4)]^{0/+}$ ), and the same system but also containing 1.5 M NaHSO<sub>4</sub> ( $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ) or 1.5 M Na<sub>2</sub>SO<sub>4</sub> ( $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ ). The  $aS_e$  corresponded to the measured  $\Delta V$  and divided by the applied  $\Delta T$ ; the  $\Delta T$  was controlled by fixing  $T_h = 40^{\circ}\text{C}$ , and varying the applied  $T_c$  between  $20^{\circ}\text{C}$  and  $35^{\circ}\text{C}$ . Second order polynomial lines of best fit have been added to guide the eye of the reader, and are not intended to model the data.


Seebeck coefficients ( $aS_e$ ) obtained at four different  $\Delta T$ , achieved by varying  $T_c$  (Fig. S2† demonstrates the similar effect achieved when varying  $T_h$ ); the fact that  $aS_e$  is not a constant value implies temperature-dependency, and explains why they have been referred to as ‘ $aS_e$ ’ rather than ‘ $S_e$ ’ throughout. The  $aS_e$  for all three systems became more negative at higher  $T_c$  values, which is indicative of a greater tendency to form ion pairs at elevated  $T$  values. This can be rationalised by considering the water of solvation: when solvated iron cations and solvated sulphate anions ion pair, several waters of solvation could be liberated with the result that ion pairing would be more entropically favoured, and would therefore increase with increasing  $T$ .

The  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  system displayed the highest degree of  $T$  sensitivity in Fig. 3, and this increased complexation at higher

$T$  values also corresponded to higher  $aS_e$  values. These significant effects upon  $aS_e$  also significantly affected the  $j_{\text{SC}}$  and  $P_{\text{max}}$  produced by  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  thermocells. Fig. 4(a) displays the different  $aS_e$  values obtained when  $\Delta T$  was fixed at 10 K, and the values of  $T_c$  and  $T_h$  simultaneously changed; upon increasing  $T_c$  from  $20^{\circ}\text{C}$  to  $40^{\circ}\text{C}$ , the  $aS_e$  value nearly doubled. This result is unusual, since typically a  $S_e$  value would remain constant or near-constant over such a narrow temperature range.<sup>42</sup> As a result, the  $j_{\text{SC}}$  and  $P_{\text{max}}$  (Fig. 4(b) and (c), respectively) also increased significantly. We have recently reported a study in the same cell assembly using 0.2 M  $\text{K}_3[\text{Fe}(\text{CN})_6]$  and 0.2 M  $\text{K}_4[\text{Fe}(\text{CN})_6]$ : fixing  $\Delta T = 10$  K and increasing  $T_c$  from  $20^{\circ}\text{C}$  to  $40^{\circ}\text{C}$  did not change  $S_e$  significantly, but increased  $P_{\text{max}}$  1.6-fold, primarily due to enhanced electron transfer kinetics and ion conduction.<sup>42</sup> This  $T_c$  effect had an even more significant effect upon the more dynamic  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  system investigated here, with  $aS_e$  doubling and  $P_{\text{max}}$  increasing 5.5-fold (from  $0.3 \text{ mW m}^{-2}$  at  $T_c = 20^{\circ}\text{C}$  to  $1.66 \text{ mW m}^{-2}$  at  $40^{\circ}\text{C}$ ). Unfortunately apparatus limitations prevent us pushing the temperature range even further.

### Spectroscopic investigation of the various iron sulphate solutions

In order to probe the potential species present, IR and UV-Vis spectroscopy were used to compare the  $[\text{Fe}(\text{SO}_4)]^{0/+}$ ,  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  systems. For UV-Vis, only Fe(III) was investigated since any Fe(II) signals are typically obscured by the much stronger Fe(III) peaks;<sup>22</sup> the solution also had to be diluted by an order of magnitude. The resulting UV-Vis spectra for all three systems are overlaid in Fig. 5; each system has two strong peaks in the ca. 220 nm and 300 nm regions, which have been previously attributed to the iron(III) hexaqua species and the  $[\text{Fe}(\text{SO}_4)]^+$  species, respectively.<sup>16,22,49</sup> Acidification with  $[\text{HSO}_4]^-$  shifts the  $\lambda_{\text{max}}$  of both features, consistent with a shift in equilibrium (as shown by eqn (3) and (5), respectively). Conversely, addition of  $[\text{SO}_4]^{2-}$  only resulted in a slight increase in the peak intensity attributed to the  $[\text{Fe}(\text{SO}_4)]^+$  species. The UV-Vis results are therefore broadly consistent with the speculated interactions, but from these spectra we were unable to accurately determine the precise speciation.

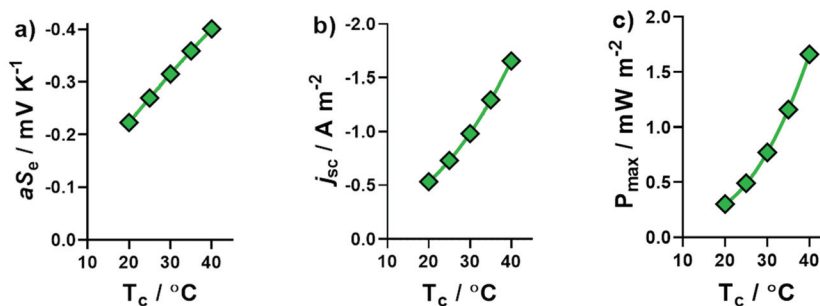

**Fig. 4** Plots showing the significant effect different applied  $T_c$  values have upon the thermogalvanic properties of the  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  system, as quantified by the (a)  $aS_e$ , (b)  $j_{\text{SC}}$ , and (c)  $P_{\text{max}}$ . For all measurements  $\Delta T = 10$  K, applied  $T_h = T_c + 10^{\circ}\text{C}$ , and applied  $T_c$  is indicated by the x-axis. Second order polynomial lines of best fit have been added to guide the eye of the reader, and are not intended to model the data.





Fig. 5 Showing (a) UV-Vis spectra and (b and c) IR spectra of dilute analogues of the  $[\text{Fe}(\text{SO}_4)]^{0/+}$  (blue lines),  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  (red lines) and  $[\text{Fe}(\text{SO}_4)_2]^{-2/-}$  (green lines) systems. Note that all used 0.03 M iron sulphate in a single oxidation state, plus 0.075 M  $\text{Na}_2\text{SO}_4/\text{NaHSO}_4$  (as applicable); (a) and (c) used 0.03 M iron(III) sulphate, and (b) used 0.03 M iron(II) sulphate.

IR was also employed in an attempt to probe the speciation; in previous IR studies a  $[\text{SO}_4]^{2-}$  peak has been reported to be centred at  $1100\text{ cm}^{-1}$ , but is known to be highly pH-dependent between pH 1 and 3, and significantly affected by the ionic strength.<sup>47</sup> Fig. 5(b) and (c) shows the IR spectra for the Fe(II) and Fe(III) systems, respectively; both exhibit peaks at  $1100\text{ cm}^{-1}$  corresponding to the asymmetric stretches of the  $[\text{SO}_4]^{2-}$  ion. All Fe-containing systems possessed small shoulders in the ca.  $980\text{ cm}^{-1}$  region, which were absent from Fe-free solutions (e.g. only  $\text{Na}_2\text{SO}_4$  and  $\text{NaHSO}_4$ , as shown in the ESI in Fig. S3†). These features have previously been assigned to distortion of the  $[\text{SO}_4]^{2-}$  upon complexation with Fe;<sup>47</sup> this is tentatively attributed here to the resulting Fe–O–S stretch. These shoulders/peaks which are related with Fe–O–S stretching (which is indicative of complexation of the  $\text{Fe}^{2+/3+}$  metal centre with  $[\text{SO}_4]^{2-}$  anions) increased for both Fe(II) and Fe(III) after the addition of  $\text{Na}_2\text{SO}_4$  or  $\text{NaHSO}_4$ , which is consistent with eqn (7); these features were significantly more pronounced in the Fe(III) systems. Furthermore, addition of  $[\text{HSO}_4]^-$  resulted in growth of a new peak at ca.  $1200\text{ cm}^{-1}$ , which has previously been attributed to the S–O–H stretch in the  $[\text{HSO}_4]^-$  ion.<sup>47</sup>

The IR results present evidence of interaction of the  $[\text{SO}_4]^{2-}$  and  $[\text{HSO}_4]^-$  anions with both the Fe(II) and Fe(III) cations, supporting the earlier thermogalvanic analysis which indicated complicated equilibria and interactions between species are present. However, since the above UV-Vis and IR results only yielded qualitative evidence of association, a more quantitative investigation of the thermoelectrochemical data was performed.

### Thermoelectrochemical determination of speciation within the thermocell

Previously, Weaver *et al.* have demonstrated that the difference in entropy of a simple redox couple ( $\Delta S_{\text{rc}}$ ) is directly proportional to  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$ , where  $Z$  is the ionic charge of the species and  $r$  is the average ionic radius.<sup>43,50</sup> The  $\Delta S_{\text{rc}}$  is given by the  $aS_{\text{e}}$ , as shown by eqn (2).

In order to test the validity of this model for the aqueous Fe(II)/Fe(III) redox system, the literature values of  $\Delta S_{\text{rc}}$  and

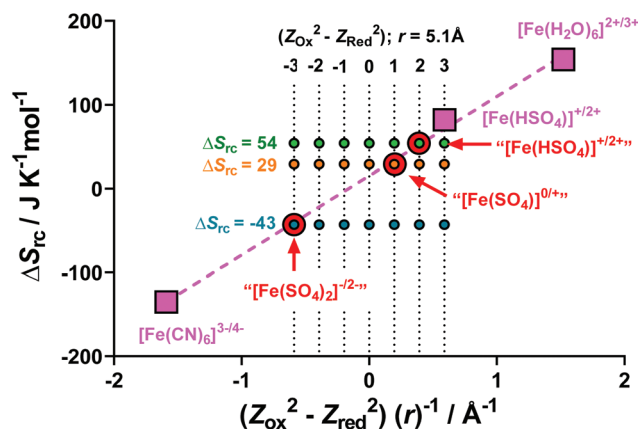


Fig. 6 Plot of  $\Delta S_{\text{rc}}$  vs.  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$  for previously reported Fe(II)/Fe(III) redox systems (pink squares) and the three Fe(II)/Fe(III) redox systems investigated here (red circles). Also shown are different calculated values of  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$  where  $r$  was fixed as  $5.1\text{ \AA}$ , and  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)$  varied, in order to quantify which  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)$  values best represent the  $[\text{Fe}(\text{SO}_4)]^{0/+}$ ,  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-2/-}$  systems investigated here.

$(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$  were used for  $[\text{Fe}(\text{H}_2\text{O})_6]^{2+/3+}$ ,<sup>22</sup>  $[\text{Fe}(\text{CN})_6]^{3-/4-}$ ,<sup>10</sup> and  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ,<sup>22</sup> (values tabulated in Table S2†). These values have been plotted in Fig. 6 (pink squares), and the expected linear relationship was observed (dashed pink line).

Next, we calculated the  $\Delta S_{\text{rc}}$  for our systems, namely  $[\text{Fe}(\text{SO}_4)]^{0/+}$ ,  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-2/-}$  (tabulated in Table S2†). Knowing the value corresponding to the y-axis, these 3 systems were plotted on Fig. 6 (indicated by red circles) using the linear  $y = mx + c$  relationship as given by the three known and previously reported systems. From this fit, the x-axis value (i.e.  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)/r$ ) for the three systems could be estimated.

A value of  $5.1\text{ \AA}$  was estimated as  $r$  for all three systems;† knowing  $r$ , seven possible  $(Z_{\text{Ox}}^2 - Z_{\text{Red}}^2)$  values were calculated,

† The ionic radius of the species ( $r$ ) was calculated from the ionic radius of the ions and postulated species present. This calculation is fully discussed in the ESI,† along with a demonstration of the effect of changing  $r$  for the determination of the species present in the system.



and these potential ( $Z_{\text{Ox}}^2 - Z_{\text{Red}}^2$ )/ $r$  are shown on Fig. 6 as a  $7 \times 3$  array. Notably, all three experimentally determined  $\Delta S_{\text{rc}}$  values fit three hypothetical ( $Z_{\text{Ox}}^2 - Z_{\text{Red}}^2$ ) values, corresponding to  $-3$ ,  $+1$  and  $+2$  for the  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ ,  $[\text{Fe}(\text{SO}_4)]^{0/+}$  and  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  systems, respectively.

The  $-3$  and  $+1$  scenarios correlate excellently with proposed species present in the “ $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ ” system (*i.e.*  $-1^2$  to  $-2^2 = -3$ ) and the “ $[\text{Fe}(\text{SO}_4)]^{0/+}$ ” system (*i.e.*  $+1^2$  to  $0^2 = +1$ ), respectively. However, the ( $Z_{\text{Ox}}^2 - Z_{\text{Red}}^2$ ) =  $+2$  scenario for the proposed “ $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ” system does not correspond to any possible combination of  $Z_{\text{Ox}}$  and  $Z_{\text{Red}}$  integers. Furthermore, the  $aS_e$  for the “ $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ” system generated here (using  $\text{NaHSO}_4$ ) is lower than the literature value reported for a  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  system, which was achieved by acidification with a large excess of  $\text{H}_2\text{SO}_4$ .<sup>4,22</sup> Therefore the “ $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ ” system investigated here using  $\text{NaHSO}_4$  likely has intermediate character between the  $[\text{FeSO}_4]^{0/+}$  and  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  systems, either as an unknown species, or more likely due to the  $aS_e$  being a mixed potential corresponding to a number of distinct species in solution, *e.g.*  $[\text{FeSO}_4]^{0/+}$  or  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ . This is likely due to the less acidic nature of  $\text{NaHSO}_4$ , relative to  $\text{H}_2\text{SO}_4$  ( $\text{p}K_a$  values of  $\text{H}_2\text{SO}_4$  and  $[\text{HSO}_4]^-$  are  $-3$  and  $1.99$ , respectively<sup>51</sup>).

With the speciation in the three interrogated thermocells determined, the redox chemistry of the three systems needed to be further investigated; this was performed with cyclic voltammetry and electrochemical impedance spectroscopy.

### Cyclic voltammetry and electrochemical impedance spectroscopy

Cyclic voltammograms (CVs) of the  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ ,  $[\text{Fe}(\text{SO}_4)]^{0/+}$  and  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  systems were measured (Fig. 7). CVs of such highly concentrated and unsupported solutions (*e.g.*  $0.6 \text{ M Fe(II)/Fe(III)}$ ), with no large excess of added supporting electrolyte leads to non-ideal responses, but is consistent with other thermoelectrochemical investigations.<sup>22</sup> All three systems gave the expected reversible electrochemistry, although notably the  $[\text{Fe}(\text{SO}_4)]^{0/+}$  system had a significantly larger peak-to-peak sep-

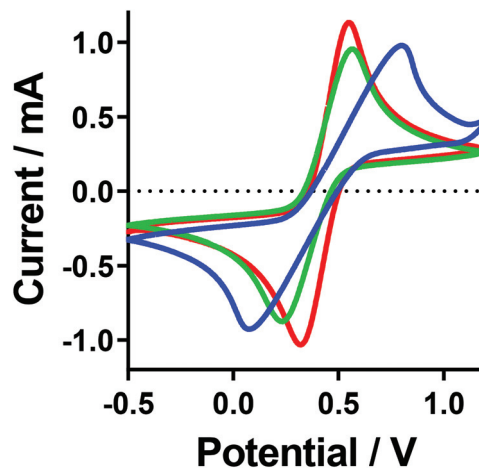


Fig. 7 Cyclic voltammograms recorded for the  $[\text{Fe}(\text{SO}_4)]^{0/+}$  (blue line),  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  (red line) and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  (green line) systems. All recorded at ambient temperature using an Au working electrode, vs. an Ag/AgCl reference electrode, at  $100 \text{ mV s}^{-1}$ . A table of data for the values can be found in the ESI.†

aration than the other two (following the trend  $[\text{Fe}(\text{SO}_4)]^{0/+} \gg [\text{Fe}(\text{SO}_4)_2]^{-/2-} > [\text{Fe}(\text{HSO}_4)]^{+/2+}$ ), which increased significantly with scan rate (Fig. S5†). This could have arisen due to either uncompensated resistance and/or slower electron transfer rates; electrochemical impedance spectroscopy was therefore employed to quantify these aspects.

Electrochemical impedance analysis was performed *in situ* in the thermocell, where the hot electrode was used as the working electrode, and the cold electrode as the counter and a Pt wire *pseudo*-reference; please note that during these measurements the cell was not generating power. These experiments were repeated with the cold electrode as the working electrode, and the same trends were observed; all impedance results can be found in the ESI.† The impedance spectra were modelled in order to determine the solution (or mass trans-

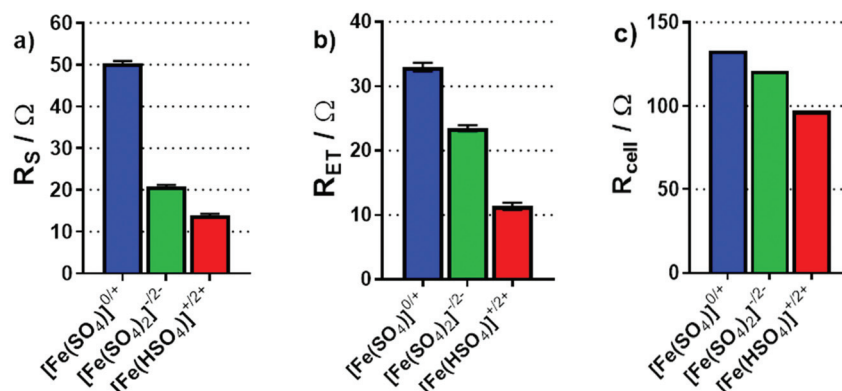


Fig. 8 Bar charts summarising (a) the solution resistance,  $R_s$  and (b) the electron transfer resistance,  $R_{\text{ET}}$ , determined through impedance spectroscopy in the non-isothermal thermocell. Also shown is (c) the calculated total thermocell resistance,  $R_{\text{cell}}$  of the thermogalvanic cell during steady-state discharge, based upon Ohm's Law ( $V = IR$ ) from  $I$ - $V$  plots during power production. All measurements were taken at an applied  $\Delta T$  of  $20 \text{ K}$  ( $T_c = 20 \text{ }^\circ\text{C}$ ). For EIS analysis, the spectra are included in the ESI,† and the fitting model has been previously reported elsewhere.<sup>22</sup>





port) resistance ( $R_S$ ) and electron transfer resistance ( $R_{ET}$ ). Fig. 8(a) and (b) display the results for the  $R_S$  and  $R_{ET}$  of the three investigated systems; both display a trend of decreasing resistance going from  $[\text{Fe}(\text{SO}_4)]^{0/+}$  to  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  to  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ . The significantly higher  $R_S$  for  $[\text{Fe}(\text{SO}_4)]^{0/+}$  is consistent with the CVs, and the two other systems having a significantly higher ionic strength, whereas the abnormally high mobility of  $\text{H}^+$  accounts for  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  having the lowest  $R_S$  value. The trend in  $R_{ET}$  follows the same order, but is less easy to explain; further work is required to determine if this is related to speciation, the electrode surface chemistry, or due to other changes (such as in the electrochemical double layer). However, the same trend was also observed at graphite electrodes (discussed later).

The overall resistance of the thermocell ( $R_{\text{cell}}$ ) during steady-state thermogalvanic discharge can also be calculated from the gradient of the  $I$ - $V$  plots measured for the three systems (from the  $V = IR$  relationship). Fig. 8(c) plots these values, which also follow the same trend as  $P_{\text{max}}$ ,  $R_S$  and  $R_{ET}$ . Notably, the  $R_{\text{cell}}$  calculated from thermogalvanic power measurements are higher than the sum of the  $R_S$  and  $R_{ET}$  values, which relate to an additional mass transfer resistance of the redox active species, as well as possible changes in  $R_S$  and  $R_{ET}$  during steady-state power generation; thermogalvanic cells which have achieved genuine steady-state<sup>42</sup> possess a concentration gradient,<sup>10</sup> given the active redox chemistry occurring at the two electrodes.

### In-parallel and in-series thermocell devices

Individual thermocells can only generate a modest potential from modest temperature gradients. This is due to the limited Seebeck coefficients (in the 0.1–1.5 mV  $\text{K}^{-1}$  range).<sup>4,22</sup> A solution to this is to combine several so-called n- and p-type thermocells (+ve and -ve  $S_e$  values, respectively) and arrange them electrically in-series but thermally in-parallel; this increases the total potential,<sup>14–17</sup> whilst avoiding a thermal short circuit.<sup>4</sup> This was therefore demonstrated, initially by combining the  $[\text{Fe}(\text{SO}_4)]^{0/+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  systems.

Fig. 9(a) displays the power curves for individual  $[\text{Fe}(\text{SO}_4)]^{0/+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  thermocells, as well as the power curve generated when combined in-series. The generated potential was nearly the sum of the two potentials, as expected; it reached only 95% of the sum due to the increased resistance of the thermocell due to the additional electrical connections.<sup>4</sup> While the overall power output can in theory be doubled by connecting thermocells in series,<sup>4</sup> here total  $P_{\text{max}}$  increased only by a factor of 1.9 (rather than 2.0) due to the internal resistance mentioned above.

Next, the same was performed but with the  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  thermocells; these two have a significantly bigger discrepancy in  $P_{\text{max}}$ , as shown in Fig. 9(b). Despite this, the potential output still essentially doubled (97% of the sum), while the overall  $P_{\text{max}}$  was 94% of the sum of two  $P_{\text{max}}$  (a factor of 1.1 with respect to  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$ , but a factor of 5.4 with respect to  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ ). This demonstrated how these systems could be combined to significantly increase the



Fig. 9 Power curves measured for individual thermocells and electrically in-series thermocells for (a)  $[\text{Fe}(\text{SO}_4)]^{0/+}$  (blue circles) and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  (green diamonds), and for (b)  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  (red squares) and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  (green diamonds). The in-series data for (a) and (b) (black inverted triangles) is offset on the x-axis to demonstrate how the potential is additive. Also (c) the power curves (filled symbols; solid lines) and  $I$ - $V$  data (hollow symbols; dashed lines) measured for an individual  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  thermocell (red squares) and two  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  thermocells electrically in-parallel (black triangles). All measurements recorded at an applied  $\Delta T$  of 20 °C ( $T_c = 20$  °C).

voltage produced by thermocell devices, and also increase the overall power output.

Given that for in-series thermocells the overall current output cannot exceed the current of a single thermocell, connection electrically in-parallel is also useful.<sup>4</sup> This serves to reduce the internal resistance, and potentially double the overall current output (once again potentially doubling the overall  $P_{\text{max}}$  output). This was evaluated for the  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  thermocells; Fig. 9(c) displays the power curve for one individ-



ual  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  thermocell and for two connected electrically in-parallel; the overall current increased by a factor of 1.8, thus boosting the overall  $P_{\text{max}}$  by a similar factor.

### Towards 'unbreakable' thermocells for thermal energy harvesting

A device was prepared comprising of 6 thermocells (full details in Experimental) in order to further boost the overall power by combining in-series 3 pairs of n-type and p-type thermocells. Following on from the results discussed above, an 'all- $\text{FeSO}_4$ -based' thermocell was prepared containing  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$ ; we were also able to explore the implications of the 'accidental' mixing of the two types of electrolytes in the device, without risk. This device now employed 12 graphite electrodes, since 12 gold electrodes were not available.

Fig. 10(a) displays the power curves generated for a 2-cell device (one  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and one  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  in-series) and for a 6-cell device (three  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and three  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  in-series; this is shown visually in Fig. 10(a)). As expected, the potential and power essentially tripled. Notably, the absolute

power from these devices are slightly lower than those discussed above, because this larger device used graphite electrodes, whereas gold was used for the investigations above; gold was a better electrocatalyst for the  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  system (as demonstrated by  $R_{\text{ET}}$  measurements; Fig. S6†).

Next, the implication of a leak resulting in complete electrolyte mixing was explored. Combining  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  and  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  results in a single solution with 0.3 M iron(II) sulphate, 0.3 M iron(III) sulphate, 0.75 M  $\text{NaHSO}_4$  and 0.75 M  $\text{Na}_2\text{SO}_4$ . Overall, this gave an  $aS_e$  of  $+0.19 \text{ mV K}^{-1}$  ( $\Delta T = 20 \text{ K}$ ,  $T_c = 20 \text{ }^\circ\text{C}$ ); the thermogalvanic characterisation of this electrolyte is further discussed in the ESI (Fig. S8–S10†). Therefore complete mixing throughout the device will result in a still-viable thermoelectrochemically-active electrolyte; however, since all 6 cells are now n-type, they cannot be operated in-series.

Fig. 10(b) displays the power curves generated by 1-cell containing the mixed electrolyte, and the 6-cell device when the electrodes were all connected to make it an electrically in-parallel device; this was achieved simply by placing a sheet of

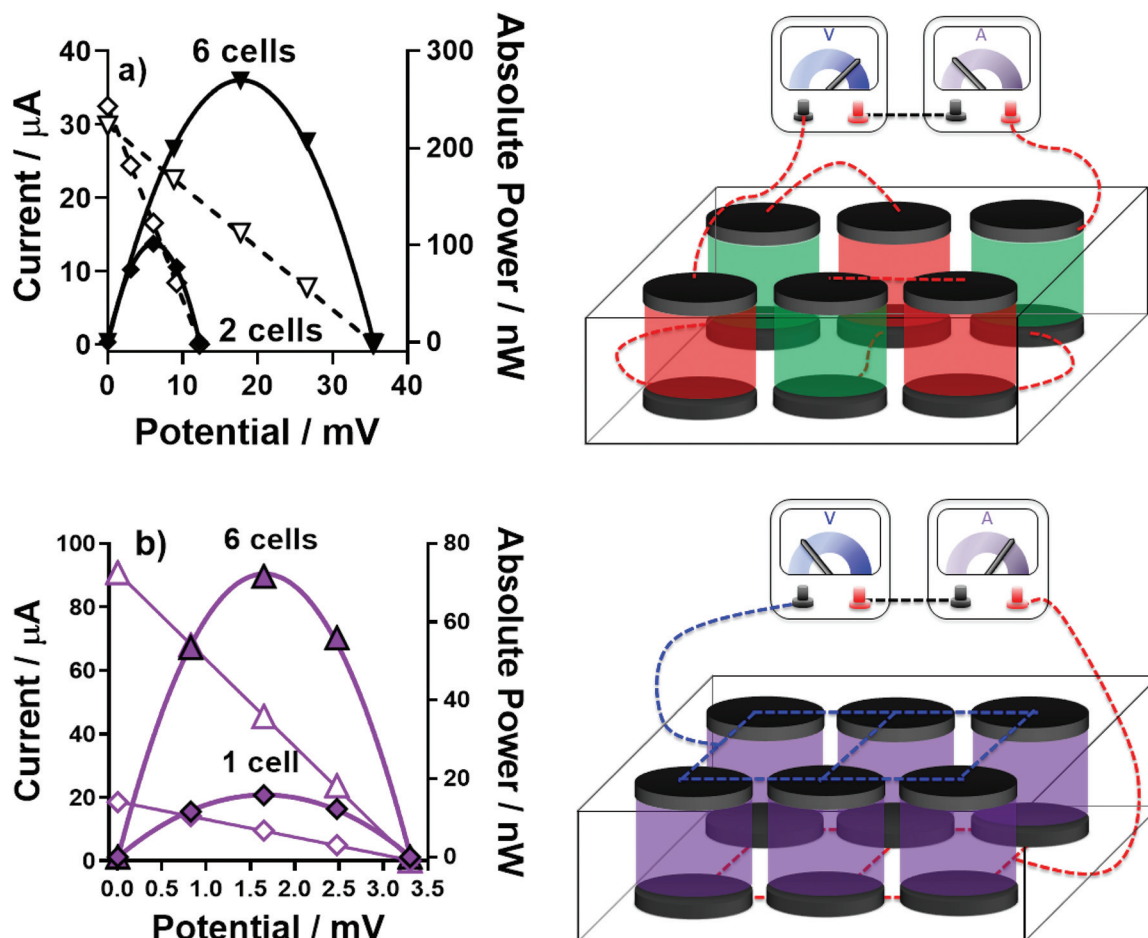


Fig. 10 Showing power curves (filled symbols; solid lines) and  $I$ - $V$  data (hollow symbols; dashed lines), as well as associated schematic cartoons, for (a) one pair of  $[\text{Fe}(\text{HSO}_4)]^{+/2+}$  –  $[\text{Fe}(\text{SO}_4)_2]^{-/2-}$  thermocells electrically in-series (black diamonds) and three pairs in-series (black inverted triangles). Similar data is shown in (b) after the two electrolytes have been mixed, showing the data for one mixed electrolyte thermocell (purple diamonds) and six mixed electrolyte thermocells electrically in-parallel (purple triangles). All measurements recorded at an applied  $\Delta T$  of 20 K ( $T_c = 20 \text{ }^\circ\text{C}$ ).



**Table 2** Table considering the 'all-FeSO<sub>4</sub> in-series thermocell' reported here, vs. the most recently published Fe<sup>2+/3+</sup> + [Fe(CN)<sub>6</sub>]<sup>3-/4-</sup> in-series thermocell from Table 1.<sup>16</sup> The two have been compared using relevant '12 Principles of Green Chemistry' and the '12 Principles of Green Engineering', considering (i) efficacy during use, and the scenario if (ii) the electrolytes are accidentally mixed, and/or (iii) released into the environment

Principles of Green Chemistry (GC) & Green Engineering (GE) (adapted from ref. 53 and 54)	HCl-acidified FeClO <sub>4</sub> and K <sub>3</sub> [NH <sub>4</sub> ] <sub>4</sub> [Fe(CN) <sub>6</sub> ] in-series thermocell (exemplified by ref. 16)	All-FeSO <sub>4</sub> in-series thermocell (this work)
- Minimise material diversity (GE 9) - Conserve complexity (GE 6)	✗ 7 elements/ molecules; complexity lost on mixing (Fe <sup>2+/3+</sup> , H <sup>+</sup> , K <sup>+</sup> , (NH <sub>4</sub> ) <sup>+</sup> , [ClO <sub>4</sub> ] <sup>-</sup> , Cl <sup>-</sup> , [Fe(CN) <sub>6</sub> ] <sup>3-/4-</sup> )	✓ 4 elements/ molecules; complexity retained on mixing (Fe <sup>2+/3+</sup> , Na <sup>+</sup> , [HSO <sub>4</sub> ] <sup>-</sup> , [SO <sub>4</sub> ] <sup>2-</sup> )
- Designing safe chemicals (GC 4) - Safer chemistry for accident prevention (GC 12) - Inputs/outputs inherently non-hazardous (GE 1)	✗ Individually safe, hazardous if mixed; [Fe(CN) <sub>6</sub> ] <sup>4-</sup> harmful to aquatic life (long lasting effects)	✓ Safe, both individually and mixed
- Design for degradation (GC 10) - Durability vs. Immortality (GE 7) - Design for commercial 'afterlife' (GE 11)	✓ Biodegradable or already elemental ✗ Mixing cannot be reversed; results in 'end-of-life'	✓ Biodegradable or already elemental ✓ Mixing enables 'second life' of thermocell
- Waste prevention (GC 1) - Waste prevention instead of treatment (GE 2)	✗ Insoluble and toxic waste generated if mixed	✓ 'Second life' can prevent waste
- Design energy efficiency (GC 6) - Maximise efficiency (GE 4)	✓ $S_e = 1.7 + 1.3 \text{ mV K}^{-1}$ $= 3.0 \text{ mV K}^{-1}$	✗ $aS_e = 0.5 + 0.3 \text{ mV K}^{-1}$ $= 0.8 \text{ mV K}^{-1}$
<b>Total number of rows thermocell is superior in</b>	2	5

graphite either side to connect all of the individual graphite electrodes. Whereas the potential output remained largely unchanged upon connecting in-parallel, the overall power was significantly boosted because of overall current was increased by a factor of 4.5.

These results indicate how two iron sulphate electrolytes can be safely used in close proximity to generate electrically in-series thermocell devices. They also demonstrate an 'unbreakable' property of the system; when mixed, the electrolyte and overall device retain functionality, providing the electrical wiring is adjusted (in an easily achieved manner). This enables a 'second life' for the electrolyte and device; 'second life' processes are currently facilitating sustainable business models and practises in the battery industry.<sup>52</sup>

### Assessing the sustainability of the all-FeSO<sub>4</sub> thermocells

In order to explore the broader green and sustainable aspects of the all-FeSO<sub>4</sub> thermocells, they were compared against the extensively-utilised thermocell combination of inherently acidic Fe<sup>2+/3+</sup> thermocells in-series with [Fe(CN)<sub>6</sub>]<sup>3-/4-</sup> thermocells. This was done using the applicable principles taken from the 12 Principles of Green Chemistry<sup>53</sup> and the 12 Principles of Green Chemical Engineering.<sup>54</sup> From these, six broad areas were identified, covering 12 principles in total; these are compared in Table 2. Comparison was based upon assuming equivalently sized thermocell devices, and the implications of their efficacy during use, and outcomes if the electrolytes were accidentally mixed and/or released into the environment.

Broadly, the complexity of the HCl-acidified Fe<sup>2+/3+</sup> + [Fe(CN)<sub>6</sub>]<sup>3-/4-</sup> in-series thermocell is a detrimental aspect, as

is the irreversible and potentially fatal nature of the side-reactions which can occur if they are heated and mixed. The main redeeming factor is that this system has a significantly higher  $S_e$ , which typically directly correlates with its efficiency at thermogalvanic heat-to-electricity conversion.<sup>20</sup> In the case of the all-FeSO<sub>4</sub> thermocell, its simplicity and its ability to have a 'second life' as a safe but thermoelectrochemically active electrolyte post-mixing results in it being a comparatively more green and sustainable system. While Table 2 focuses solely upon the latest publication<sup>16</sup> from Table 1, all reports in Table 1 share similar features (*e.g.* complex, harmful components which are hazardous if mixed, but all also provide higher  $S_e$  values with summed values between 1.5 and 3.2 mV K<sup>-1</sup>). What is required now for the all-FeSO<sub>4</sub> thermocell is further research in order to boost the thermogalvanic efficiency and power of such systems, to enable even more effective 'waste heat-to-electricity' conversion opportunities. To achieve this, dynamic systems such as those demonstrated here need to be harnessed, but achieve even greater ( $Z_{\text{ox}}^2 - Z_{\text{red}}^2$ )/ $r$  values.

## Conclusions

In this study it was demonstrated how an inversion of the Seebeck coefficient ( $S_e$ ) could be achieved in an all-iron-sulphate thermogalvanic system, to achieve the equivalent of both the n-type and p-type systems common to thermoelectric devices. While the  $S_e$  of aqueous iron(II/III) sulphate solutions ( $S_e = ca. +0.3 \text{ mV K}^{-1}$ ) and their acidified analogues ( $S_e = ca. +0.9 \text{ mV K}^{-1}$ ) have been previously reported, we report here that much milder acidification can be achieved with NaHSO<sub>4</sub>,



while still almost doubling the  $S_e$  to  $+0.57 \text{ mV K}^{-1}$ . Conversely, it was demonstrated for the first time that  $\text{Na}_2\text{SO}_4$  can be added to invert the entropic direction of the thermogalvanic process in the p-type direction, with a  $S_e$  of  $-0.4 \text{ mV K}^{-1}$  easily achieved. It was further demonstrated how these two novel systems can be combined electrically in-series, to additively boost the  $S_e$  of the combined device, and thus increase overall thermogalvanic power output. For example, combining 2-cells in-series generated 97% of the sum of the power of the individual cells; moving from 2-cells to 6-cells essentially tripled the power output.

These all-iron-sulphate thermogalvanic systems are less powerful than the comparatively more investigated  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  thermocells, as demonstrated clearly by their combined Seebeck coefficients being *ca.* 25% of the 'state-of-the-art' value<sup>14</sup> ( $0.8 \text{ vs. } 3.2 \text{ mV K}^{-1}$ , respectively). However, research into the aforementioned systems has not focussed upon introducing any safer thermocells or combinations to reduce the potential hazards; existing reports instead contain an inherent risk of hydrogen cyanide gas release. It was clearly demonstrated here that mixing of the all-iron-sulphate thermogalvanic electrolytes could occur safely, and even retain functionality as a mixed electrolyte system ( $S_e = +0.19 \text{ mV K}^{-1}$ ) thus demonstrating a potential 'second life' application of this system.

The novel iron(II/III) sulphate systems presented here are proposed as more benign alternatives to the conventional  $\text{Fe}^{2+/3+}$  and  $[\text{Fe}(\text{CN})_6]^{3-/4-}$  thermocells, which are potentially lethal if combined. The thermoelectrochemically quantified  $\Delta S_{\text{rc}}$  values for the thermocells also allowed a detailed and quantitative analysis of the speciation. This could be employed in the future to probe other concentration-dependent transitions, and potentially those triggered by pH, solvent, *etc.* This study also highlights the need to carefully consider the 'what if' aspects of thermocells, including their potential for mixing, and their 'end-of-life' and even 'second life' possibilities.

## Conflicts of interest

The authors have no conflicts of interest to declare.

## Acknowledgements

M. A. B. acknowledges the EPSRC for funding (Standard Research Studentship (DTP), EP/N509498/1).

## References

- 1 T. I. Quickenden and Y. Mua, *J. Electrochem. Soc.*, 1995, **142**, 3985–3994.
- 2 Fitriani, R. Ovik, B. D. Long, M. C. Barma, M. Riaz, M. F. M. Sabri, S. M. Said and R. Saidur, *Renewable Sustainable Energy Rev.*, 2016, **64**, 635–659.
- 3 L. B. Kong, T. Li, H. H. Hng, F. Boey, T. Zhang and S. Li, *Waste Energy Harvesting*, 2014, vol. 24.
- 4 M. Al Maimani, J. J. Black and L. Aldous, *Electrochem. Commun.*, 2016, **72**, 181–185.
- 5 A. Montecucco, J. Siviter and A. R. Knox, *Appl. Energy*, 2014, **123**, 47–54.
- 6 C. B. Vining, *Nat. Mater.*, 2009, **8**, 83–85.
- 7 Endangered Elements, <https://www.acs.org/content/acs/en/greenchemistry/research-innovation/endangered-elements.html>.
- 8 G. Tan, L. D. Zhao and M. G. Kanatzidis, *Chem. Rev.*, 2016, **116**, 12123–12149.
- 9 J. Wu, J. J. Black and L. Aldous, *Electrochim. Acta*, 2017, **225**, 482–492.
- 10 B. Burrows, *J. Electrochem. Soc.*, 1976, **123**, 154–159.
- 11 T. I. Quickenden and C. F. Vernon, *Sol. Energy*, 1986, **36**, 63–72.
- 12 S. G. Bratsch and J. Phys, *Chem. Ref. Data*, 1989, **18**, 1–21.
- 13 J. J. Black, T. Murphy, R. Atkin, A. Dolan and L. Aldous, *Phys. Chem. Chem. Phys.*, 2016, **18**, 20768–20777.
- 14 J. H. Kim, J. H. Lee, R. R. Palem, M. S. Suh, H. H. Lee and T. J. Kang, *Sci. Rep.*, 2019, **9**, 8706.
- 15 L. Zhang, T. Kim, N. Li, T. J. Kang, J. Chen, J. M. Pringle, M. Zhang, A. H. Kazim, S. Fang, C. Haines, D. Al-Masri, B. A. Cola, J. M. Razal, J. Di, S. Beirne, D. R. MacFarlane, A. Gonzalez-Martin, S. Mathew, Y. H. Kim, G. Wallace and R. H. Baughman, *Adv. Mater.*, 2017, **29**, 1605652.
- 16 K. Kim, S. Hwang and H. Lee, *Electrochim. Acta*, 2020, **335**, 135651.
- 17 P. Yang, K. Liu, Q. Chen, X. Mo, Y. Zhou, S. Li, G. Feng and J. Zhou, *Angew. Chem., Int. Ed.*, 2016, **55**, 12050–12053.
- 18 H. Jia, Z. Ju, X. Tao, X. Yao and Y. Wang, *Langmuir*, 2017, **33**, 7600–7605.
- 19 Y. Liang, J. K. H. Hui, T. Yamada and N. Kimizuka, *ChemSusChem*, 2019, **12**, 4014–4020.
- 20 L. Aldous, J. J. Black, M. C. Elias, B. Gélinas and D. Rochefort, *Phys. Chem. Chem. Phys.*, 2017, **19**, 24255–24263.
- 21 J. Duan, B. Yu, K. Liu, J. Li, P. Yang, W. Xie, G. Xue, R. Liu, H. Wang and J. Zhou, *Nano Energy*, 2019, **57**, 473–479.
- 22 M. A. Buckingham, F. Marken and L. Aldous, *Sustainable Energy Fuels*, 2018, **2**, 2717–2726.
- 23 M. A. Buckingham, S. Hammoud, H. Li, C. J. Beale, J. T. Sengel and L. Aldous, *Sustainable Energy Fuels*, 2020, **4**, 3388–3399.
- 24 C. A. P. Arellano and S. S. Martinez, *Sol. Energy Mater. Sol. Cells*, 2010, **94**, 327–332.
- 25 S. Asperger, *Trans. Faraday Soc.*, 1952, **48**, 617–624.
- 26 S. Asperger, I. Murati and D. Pavlovic, *J. Chem. Soc.*, 1953, 730–736.
- 27 J. M. Kruse and L. E. Thibault, *Anal. Chem.*, 1973, **45**, 2260–2261.
- 28 P. L. Domingo, B. Garcia and J. M. Leal, *Can. J. Chem.*, 1990, **68**, 228–235.



- 29 H. Basset and A. S. Corbet, *J. Chem. Soc. Trans.*, 1924, 1358–1366.
- 30 A. S. Brar, H. S. Sandhu and H. S. Sandhu, *Thermochim. Acta*, 1980, **41**, 253–256.
- 31 A. S. Brar, H. S. Sandhu and S. S. Sandhu, *J. Therm. Anal.*, 1983, **26**, 7–15.
- 32 A. S. Brar, H. Singh, S. Brar and B. S. Randhawa, *J. Therm. Anal.*, 1981, **21**, 77–88.
- 33 J. I. Kunrath, C. S. Müller and E. Frank, *J. Therm. Anal.*, 1978, **14**, 253–264.
- 34 M. Ruiz-Bermejo, C. Rogero, C. Menor-Salván, S. Osuna-Esteban, J. Á. Martín-Gago and S. Veintemillas-Verdaguer, *Chem. Biodivers.*, 2009, **6**, 1309–1322.
- 35 A. C. L. Câmara and B. Soto-Blanco, Cyanide poisoning in animals and humans, *Cyanide: Occurrence, Characteristics and Applications*, ed. B. Soto-Blanco, Nova Science Publishers, Inc., 2013, pp. 23–46.
- 36 F. Musshoff, K. M. Kirschbaum and B. Madea, *Forensic Sci. Int.*, 2011, **204**, e4–e7.
- 37 A. H. Hall and B. H. Rumack, *Ann. Emerg. Med.*, 1986, **15**, 1067–1074.
- 38 H. A. H. Alzahrani, M. A. Buckingham, F. Marken and L. Aldous, *Electrochem. Commun.*, 2019, **102**, 41–45.
- 39 Sigma-Aldrich, Potassium ferricyanide(III) – SDS, <https://www.sigmaaldrich.com/MSDS/MSDS/DisplayMSDSPage.do?country=GB&language=en&productNumber=702587&brand=SIGALD&PageToGoToURL=https%3A%2F%2Fwww.sigmaaldrich.com%2Fcatalog%2Fsearch%3Fterm%3DPotassium%2Bferricyanide%26interface%3DAll%26N%3D0%26mode%3Dpar>, (accessed 18 May 2020).
- 40 Sigma-Aldrich, Potassium hexacyanoferrate(II) trihydrate – SDS, <https://www.sigmaaldrich.com/MSDS/MSDS/DisplayMSDSPage.do?country=GB&language=en&productNumber=P3289&brand=SIGALD&PageToGoToURL=https%3A%2F%2Fwww.sigmaaldrich.com%2Fcatalog%2Fsearch%3Fterm%3Dpotassium%2Bferrocyanide%26interface%3DAll%26N%3D0%26mode%3Dpar>, (accessed 18 May 2020).
- 41 Hydrogen Cyanide, [https://www.cdc.gov/niosh/ershdb/emergencyresponsecard\\_29750038.html](https://www.cdc.gov/niosh/ershdb/emergencyresponsecard_29750038.html), (accessed 18 May 2020).
- 42 M. A. Buckingham and L. Aldous, *J. Electroanal. Chem.*, 2020, DOI: 10.1016/j.jelechem.2020.114280.
- 43 J. T. Hupp and M. J. Weaver, *Inorg. Chem.*, 1984, **23**, 3639–3644.
- 44 L. L. Trent, R. S. Hestand and C. C. Carter, *J. Aquat. Plant Manage.*, 1978, **16**, 40–43.
- 45 N. N. Greenwood and A. Earnshaw, *Chemistry of the Elements*, Pergamon Press Ltd., Leeds, 1984.
- 46 R. J. Lemire, U. Berner, C. Musikas, D. A. Palmer, P. Taylor and O. Tochiyama, *Chemical thermodynamics of iron Part 1, OECD*, 2013, vol. 13a.
- 47 J. Majzlan and S. C. B. Myneni, *Environ. Sci. Technol.*, 2005, **39**, 188–194.
- 48 E. H. B. Anari, M. Romano, W. X. Teh, J. J. Black, E. Jiang, J. Chen, T. Q. To, J. Panchompoo and L. Aldous, *Chem. Commun.*, 2016, **52**, 745–748.
- 49 F. J. Millero, W. Yao and J. Aicher, *Mar. Chem.*, 1995, **50**, 21–39.
- 50 J. T. Hupp and M. J. Weaver, *J. Phys. Chem.*, 1984, **88**, 1860–1864.
- 51 D. H. Ripin and D. A. Evans, *pKa's of Inorganic and Oxo-Acids*, 2005, [http://evans.rc.fas.harvard.edu/pdf/evans\\_pKa\\_table.pdf](http://evans.rc.fas.harvard.edu/pdf/evans_pKa_table.pdf) (accessed 2020).
- 52 N. Jiao and S. Evans, *Procedia CIRP*, 2016, **40**, 250–255.
- 53 P. Anastas and J. Warner, *Green Chemistry: Theory and Practice*, Oxford University Press, Oxford [England], 2000.
- 54 P. T. Anastas and J. B. Zimmerman, *Environ. Sci. Technol.*, 2003, **37**, 94A–101A.

