

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Mater. Adv.*, 2023,  
4, 1604Redox-active, porous pyrene tetraone dendritic  
polymers as cathode materials for lithium-ion  
batteries†Lucas Ueberricke,<sup>a</sup> Felix Mildner,<sup>a</sup> Yuquan Wu,<sup>b</sup> Elisa Thauer,<sup>id b</sup>  
Tom Wickenhäuser,<sup>b</sup> Wen-Shan Zhang,<sup>c</sup> Yana Vaynzof,<sup>id bd</sup> Sven M. Elbert,<sup>a</sup>  
Rasmus R. Schröder,<sup>c</sup> Rüdiger Klingeler<sup>\*b</sup> and Michael Mastalerz<sup>id \*a</sup>Received 18th November 2022,  
Accepted 26th February 2023

DOI: 10.1039/d2ma01039a

[rsc.li/materials-advances](https://rsc.li/materials-advances)

Redox active, insoluble pyrene tetraone based dendritic porous polymers were synthesized by using different catalyst loadings and work-up procedures. The dendritic polymers were investigated by gas sorption analysis for their porosity and characterized with respect to their properties as active material in cathodes of lithium ion secondary batteries. Electrochemical measurements by means of cyclic voltammetry and galvanostatic cycling show reversible redox activity and specific capacities of up to 137 mA h g<sup>-1</sup> with a capacity retention of 86% after 50 cycles.

## Introduction

The commercialization of lithium-ion batteries (LIBs) in 1991 was a milestone in the field of mobile energy storage. Due to their longevity, high voltage, high capacity and good rechargeability these devices are nowadays widely used in many electronic devices, such as smartphones, laptops and even electric vehicles – a development for which Goodenough, Whittingham and Yoshino were awarded the Nobel prize in 2019.<sup>1</sup> However, to meet the increasing demand for highly efficient, low-cost and environmental friendly energy sources, the development of advanced LIBs based on affordable and sustainable resources is required. For the realization of high-performance batteries, the search for suitable cathode materials and their optimization is of crucial importance, as it is one of the most critical factors.<sup>2</sup> Recent attention has shifted towards using organic instead of inorganic cathode materials in search for more light-weight, metal-free and flexible batteries.<sup>3–6</sup> In addition, the structural diversity of organic compounds allows to widely tune their electrochemical

properties. Organic compounds bearing redox-active functionalities, *e.g.* carbonyls (quinones, imides, anhydrides),<sup>7–22</sup> nitroxyl radicals<sup>23–25</sup> or disulfides<sup>26,27</sup> are promising candidates due to their typical redox potentials between 2.0 V and 4.0 V *vs.* Li/Li<sup>+</sup> and have been widely studied for this purpose. To overcome dissolution issues, which usually result in capacity decay upon cycling, the redox active sites are often either incorporated into or attached to a polymeric backbone<sup>3,4</sup> or larger, rigid groups that reduce solubility in the electrolyte are attached.<sup>14–16</sup> Quinones are of special interest for application as cathode material due to their multi-electron redox activity, high energy density and electronic stability.<sup>7,10</sup> For example, an exceptionally high capacity of 902 mA h g<sup>-1</sup> and 82% capacity retention after 100 cycles at 20 mA g<sup>-1</sup> in an ionic liquid electrolyte was reported for cyclohexanhexone.<sup>19</sup> Among this class of compounds, pyrene-4,5,9,10-tetraone (PTO) is another outstanding candidate, as all four carbonyl positions can be utilized for the redox process for the uptake of four Li<sup>+</sup> ions with a high operating voltage (above 1.5 V). The full redox capability of all four carbonyl groups can be attributed to the stable highest occupied molecular orbital of PTO and the aromaticity upon reduction. Thus, the theoretical capacity of PTO is high (409 mA h g<sup>-1</sup>).<sup>8,12,18</sup> Experimentally a capacity of 360 mA h g<sup>-1</sup> was found, however accompanied by low cycling stability due to dissolution.<sup>8</sup> Various immobilization attempts of PTO have been studied in recent years (Scheme 1). In 2012 Yoshida and coworkers attached PTO to a polymethacrylate backbone *via* an amide linkage. The obtained PPYT showed a high capacity of 231 mA h g<sup>-1</sup> (88% of the theoretical capacity) and a high capacity retention of 83% after 500 cycles.<sup>12</sup>

By covalent binding PTO to an sp<sup>2</sup>-carbon surface (PYT-C), Karunadasa *et al.* achieved a capacity of 123 mA h g<sup>-1</sup> and 55%

<sup>a</sup> Organisch-Chemisches Institut, Ruprecht-Karls-Universität Heidelberg, Im Neuenheimer Feld 270, Heidelberg 69120, Germany.

E-mail: Michael.mastalerz@oci.uni-heidelberg.de


<sup>b</sup> Kirchhoff-Institut für Physik, Ruprecht-Karls-Universität Heidelberg, Im Neuenheimer Feld 227, Heidelberg 69120, Germany.

E-mail: klingeler@kip.uni-heidelberg.de

<sup>c</sup> BioQuant, Ruprecht-Karls-Universität Heidelberg, Im Neuenheimer Feld 267, Heidelberg 69120, Germany

<sup>d</sup> Technical University of Dresden (TUD), Integrated Center for Applied Physics and Photonic Materials (IAPP) and Center for Advancing Electronics Dresden (cfaed), Dresden 01062, Germany


† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ma01039a>

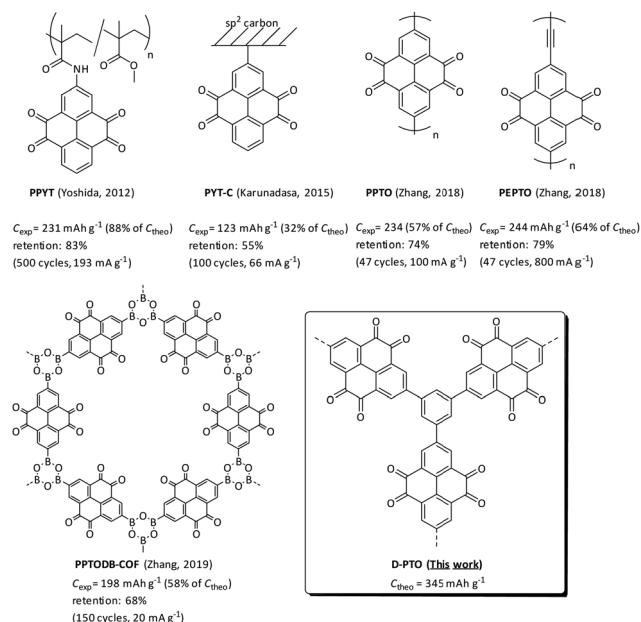

**Scheme 1** Examples of **PTO** based materials used as cathodes and corresponding capacities and capacity retentions.

retention after 100 cycles at 66  $\text{mA g}^{-1}$ .<sup>13</sup> Two linear polymers **PPTO** and **PEPTO** with capacities of 234–244  $\text{mA h g}^{-1}$  (57–64% of theoretical values) and 74–79% retention after 47 cycles were reported by Zhang and coworkers in 2018.<sup>18</sup> One year later, a 2D boroxine covalent organic framework (COF) was published by the same group. **PPTODB-COF** showed a capacity of 198  $\text{mA h g}^{-1}$  (58% of the theoretical value) and 68% retention after 150 cycles at 20  $\text{mA g}^{-1}$ .<sup>20</sup> Another recently reported pyrene tetraone based COF by Zheng *et al.* showed reversible capacity of 225  $\text{mA h g}^{-1}$  and an exceptional long-term cyclability (retention rate 98.0% after 10 000 cycles) in aqueous zinc–organic batteries.<sup>28</sup> Carbonyl-based composites with carbon nanotubes reached capacities of 438  $\text{mA h g}^{-1}$ <sup>29</sup> and 416  $\text{mA h g}^{-1}$ .<sup>30</sup> Despite this progress some challenges still remain. Except for **PPYT**, the experimental capacities are much smaller than theoretically possible and usually reach only little more than 50% of the theoretical capacity, indicating that only half of the redox-active sites are actually utilized. This still leaves room for improvement, as capacities higher than 200  $\text{mA h g}^{-1}$  are desirable.

Another parameter, which tends to be much lower in organic as compared to inorganic materials, is the rate capability and often slow redox kinetics limits the power density. Both might be attributed to the lack of Li-ion channels in many organic materials that allow efficient ion diffusion.<sup>14</sup> Thus, porous structures seem to be beneficial and materials with high surface areas have shown improved device performance, for example in metal organic frameworks (MOFs)<sup>5,31–34</sup> or covalent organic frameworks (COFs).<sup>5,35–38</sup> In the examples given in Scheme 1 pores could be seen by electron microscopy (EM) imaging for **PPYT** and for **PYT-C** a high-surface carbon source was used. **PPTODB-COF** most likely has channels for  $\text{Li}^+$  diffusion due to its rigid 2D framework, whereas **PPTO** and **PEPTO** are most

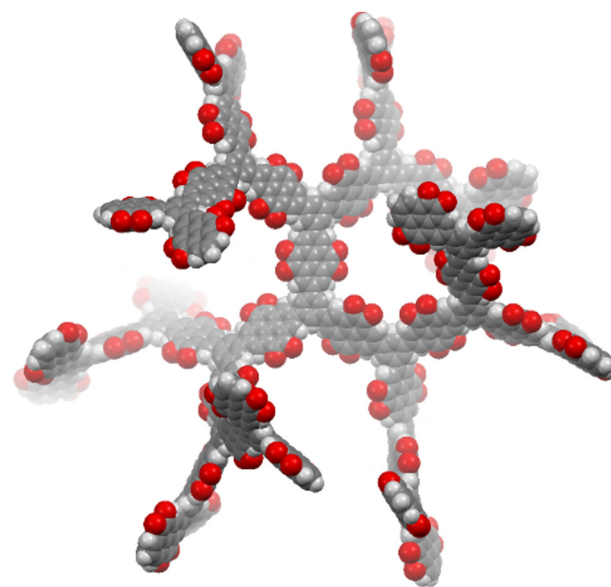

**Fig. 1** Proposed structural cutout of **D-PTO** (MM2 model).

likely non-porous. However, the porosity of none of those materials was investigated by gas sorption analysis.


Here we present the synthesis of an insoluble porous dendritic polymer network (**D-PTO**), where **PTO** monomers are connected *via* the *meta*-positions of a benzene unit. We envisioned, that the rigidity of this structure prevents close-packing, thereby opening up channels for ion and electrolyte diffusion. At the same time, we expected low solubility. The porous structure was simulated by MM2 optimization of an oligomeric cutout (Fig. 1). **D-PTO** is expected to form a rigid, dendrimer-like structure, where the individual branches form helical channels with an approx. diameter of 1.4 nm. The porosity was investigated by gas sorption and the material was investigated regarding its performance as cathode material in LIBs.

## Results and discussion

### Synthesis

In order to construct a branched, rigid network dendrimeric pyrene tetraketals (**D-PTK**) were synthesized *via* Suzuki–Miyaura cross coupling of borylated tetraketale **3**<sup>39</sup> with 1,3,5-tribromo benzene **4** (Scheme 2). After a few minutes of heating, the formation of a large amount of grey solid preventing further stirring was observed (see the ESI† for details). Different catalyst loadings (2%, 6%, 10%) **D-PTK-1**, **-2** and **-3**, respectively, and from these precursor polymers the corresponding target materials **D-PTO-1**, **-2a** and **3** were subsequently obtained *via* acidic hydrolysis as red powders (see the ESI† for details). **D-PTO-2a** was further purified by Soxhlet extraction (MeOH, THF, Et<sub>2</sub>O) to obtain **D-PTO-2b**. By this procedure remaining pyrene tetraone monomer could be extracted, showing that washing alone was not sufficient to remove unreacted starting material. The prepared **D-PTOs** were insoluble in common organic solvents,



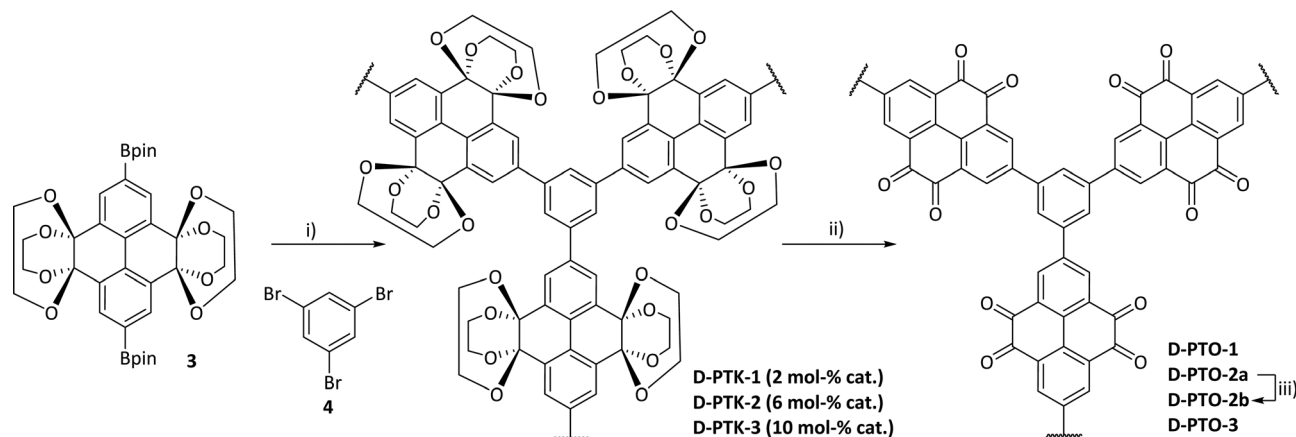

**Scheme 2** Model compounds **1** and **2** and **D-PTO** synthesis (conditions: (i) 2–10 mol%  $\text{Pd}_2(\text{dba})_3$ , 1 M  $\text{K}_2\text{CO}_3$ , THF, Ar, 85 °C, 14–18 h, 85%. (ii) 1. TFA/ $\text{H}_2\text{O}$  (9:1), 24 h, rt, 2. 1 M  $\text{H}_2\text{SO}_4$ , 1 h, rt, 95%). (iii) Soxhlet extraction (MeOH, THF,  $\text{Et}_2\text{O}$ ). **D-PTO-1**, **-2a** and **-3** were prepared from the corresponding **D-PTK-1**, **-2**, and **-3** batch, respectively.

such as MeOH, EtOH, acetone,  $\text{CHCl}_3$ ,  $\text{CH}_2\text{Cl}_2$ , diethyl ether, petroleum ether and water.

### Optoelectronic characterization of model compounds

A ketal and a tetraone model compound **1** and **2** (see the ESI<sup>†</sup>) were synthesized according to a recently published procedure.<sup>40</sup> These compounds have a similar structure as the polyketal **D-PTK** and polytetraone **D-PTO** respectively, and are soluble in common organic solvents. Therefore, they can be investigated *via* standard solution-based techniques. Spectroscopic characteristics of the polymers can thus easily be evaluated by comparison with the corresponding model compound. The optoelectronic properties of tetraone **2** were investigated by UV/Vis spectroscopy in  $\text{CH}_2\text{Cl}_2$  and liquid-3-electrode cyclic voltammetry (CV) in  $\text{CH}_2\text{Cl}_2$  with ferrocene/ferrocenium ( $\text{Fc}/\text{Fc}^+$ ) as internal standard and quantum-chemical calculations (Fig. 2). The UV/Vis spectrum revealed two absorption maxima at  $\lambda_{\text{abs}} = 283$  and 457 nm. From the absorption onset at  $\lambda_{\text{onset}} = 560$  nm an optical bandgap of  $E_{\text{g,opt}} = 2.2$  eV was determined. CV revealed two quasi-reversible half-wave reduction

potentials at  $E_{\text{red},1} = -0.90$  V and  $E_{\text{red},2} = -1.26$  V. From the first reduction potential the electron affinity of  $\text{EA} = -3.9$  eV was estimated. An ionization potential of  $\text{IP} = -6.1$  eV was approximated from the optical bandgap.

DFT calculations (B3LYP: 6-311++G\*\*) showed that the HOMO orbital ( $E_{\text{HOMO}} = -6.8$  eV) is delocalized over the whole aromatic backbone, while the LUMO orbital ( $E_{\text{LUMO}} = -3.8$  eV) is located only on the pyrene tetraone unit.


### Polymer analysis and characterization

Dendrimer materials were analyzed by  $^{13}\text{C}$  MAS NMR spectroscopy, FT-IR spectroscopy (ATR), elemental analysis and X-ray photoelectron spectroscopy (XPS). Further, the materials were investigated by thermogravimetric analysis (TGA), powder X-ray diffraction, SEM and gas sorption measurements.

By comparison of FT-IR spectra (Fig. 3), both ketal **1** and the **D-PTKs** showed similar absorption patterns with characteristic C–H valence vibration bands at  $\sim 2954$   $\text{cm}^{-1}$  and  $2864$   $\text{cm}^{-1}$ , indicating the presence of saturated C–H groups. Similarly, an intense band at  $\sim 1098$   $\text{cm}^{-1}$  can be attributed to the C–O valence vibration, thus showing the presence of ketal groups. The spectra of tetraone model compound **2** and **D-PTO** also had very similar peak patterns. An intense band at  $\sim 1672$   $\text{cm}^{-1}$  in both spectra proves the presence of carbonyl functions. At the same time the C–H valence vibration bands vanished for **D-PTOs**, indicating the loss of the ketal units.

**D-PTO-2a** and its precursor material were investigated by  $^{13}\text{C}$  MAS NMR and compared with  $^{13}\text{C}$  NMR spectra of model compounds **1** and **2** obtained from solution (Fig. 4). The signal at  $\sim 93$  ppm is indicative for the ethylene bridges  $\text{C}^{\text{a}}$  and can be found in both model compound **1** and **D-PTK-2a**. After deprotection to **D-PTO-2a** this signal vanishes almost completely and a new signal at  $\delta = 181.9$  ppm, characteristic for the carbonyl carbons  $\text{C}^{\text{b}}$ , appears. This shows that except some trace amounts, the acid treatment effectively hydrolyzes the ketal groups.

The elemental composition and purity of the **D-PTO** materials was determined by elemental analysis and XPS

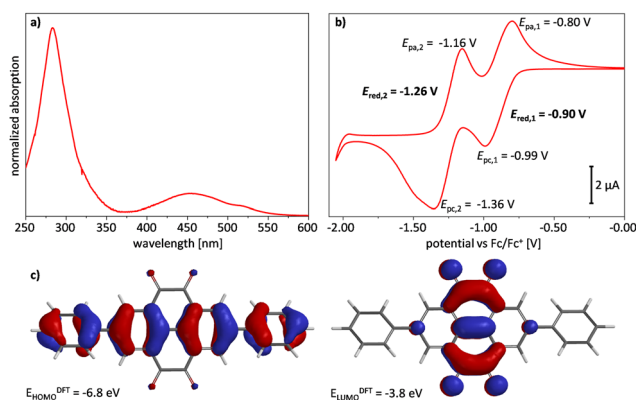

**Fig. 2** (a) UV/Vis spectrum of compound **2** measured in  $\text{CH}_2\text{Cl}_2$  at  $1 \mu\text{mol L}^{-1}$ . (b) Cyclic voltammogram of model compound **2** ( $\text{CH}_2\text{Cl}_2$ ,  $n\text{Bu}_4\text{NPF}_6$  (0.1 M), measured at rt with Pt-working electrode and  $\text{Fc}/\text{Fc}^+$ ) as internal reference, scanning velocity: 100  $\text{mV s}^{-1}$ . (c) DFT model (B3LYP: 6-311++G\*\*) of compound **2** (tert-butyl groups omitted).

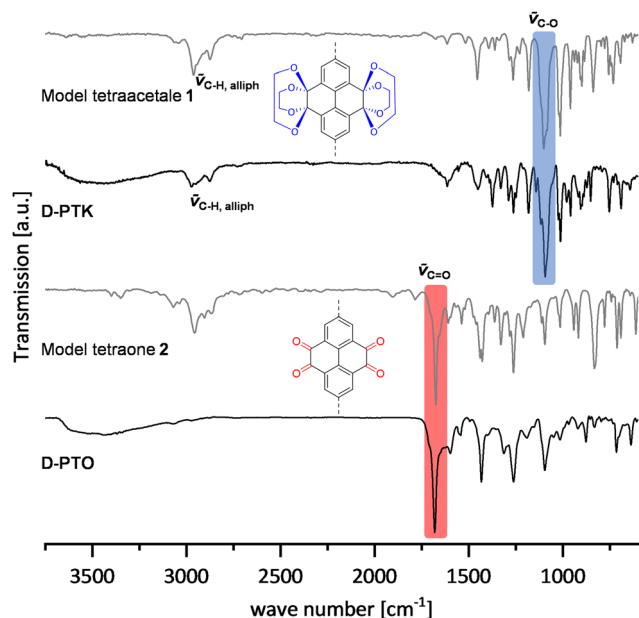


Fig. 3 FT-IR spectra (ATR) of **D-PTK**, **D-PTO** and model compounds **1** and **2**.

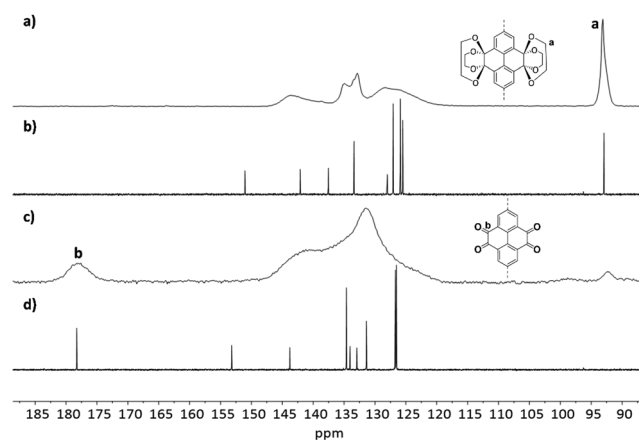


Fig. 4  $^{13}\text{C}$  CP MAS NMR spectra (10 000 Hz) of **D-PTK 2** (a), **D-PTO 2a** (c) and  $^{13}\text{C}$  NMR spectra ( $\text{CDCl}_3$ , 150 MHz) of model compounds **1** (b) and **2** (d).

measurements. For **D-PTO-1** trace residues of two different Pd species from residual catalyst traces and bromide (below 1% each) were found, indicating that some bromide groups remained unreacted (Fig. S5 and Table S3, ESI†). The elemental

analysis for carbon and hydrogen is in good agreement with the theoretical values, when adsorbed water is considered. XPS measurement on **D-PTO-2** and **D-PTO-3** showed no traces of Pd, and also no bromide could be found (Fig. S6–S8 and Tables S4–S6, ESI†), indicating that lower catalyst loading is beneficial for material purity. Boron containing species (1.49%) found in **D-PTO-2a** could be completely removed by Soxhlet extraction. The extraction step is therefore also beneficial for the degree of purity.

All **D-PTOs** were characterized by TGA under nitrogen atmosphere. Decomposition of the materials were observed in between 285–312 °C, after an initial weight loss up to ~100 °C due to solvent evaporation. The decomposition temperature did not show a clear correlation to reaction conditions (*i.e.*, catalyst loading) and differ for each batch. Table 1 and Fig. 5 summarize the properties of the prepared materials.

The morphology and crystallinity of **D-PTO** was investigated using SEM imaging (Fig. 5a) and PXRD (Fig. S10, ESI†). Both methods reveal that the **D-PTOs** are mostly amorphous (see the ESI†). However, **D-PTO-1** shows two peaks at  $2\theta = 40$  and  $46^\circ$ , which are either absent or very weak in the other materials.

Gas sorption analysis with nitrogen at 77 K of **D-PTO-1** showed a type-I isotherm with a specific surface area ( $\text{SA}_{\text{BET}}$ )<sup>41</sup> of  $\text{SA}_{\text{BET}} = 290 \text{ m}^2 \text{ g}^{-1}$ , revealing the porous nature of the material (Fig. 5b and c). By QS-DFT calculation (Kernel:  $\text{N}_2$  on carbon at 77 K, sphere/cylindrical pores, adsorption branch, fitting error: 0.420%)<sup>42,43</sup> a pore diameter of  $d_{\text{pore,max}} = 0.67 \text{ nm}$  is obtained (Fig. 5c). The microporous surface area is 59% of the overall surface area as calculated by the *t*-plot method<sup>44–46</sup> with a pore volume of  $V_{\text{pore,micro}} = 0.07 \text{ cm}^3 \text{ g}^{-1}$ .

For **D-PTO-2a** an increased specific surface area of  $\text{SA}_{\text{BET}} = 472 \text{ m}^2 \text{ g}^{-1}$  with a doubling in pore diameter ( $d_{\text{pore,max}} = 1.27 \text{ nm}$ ) compared to **D-PTO-1** was found (Kernel:  $\text{N}_2$  on carbon at 77 K, sphere/cylindrical pores, adsorption branch, fitting error: 0.755%). A larger fraction of microporous surface area (71%) and an increased pore volume ( $V_{\text{pore,micro}} = 0.136 \text{ cm}^3 \text{ g}^{-1}$ ) was estimated. **D-PTO-2b**, which was prepared from **D-PTO-2a** *via* Soxhlet extraction, shows a slightly increased specific surface area ( $\text{SA}_{\text{BET}} = 537 \text{ m}^2 \text{ g}^{-1}$ ), and pore volume ( $V_{\text{pore,micro}} = 0.146 \text{ cm}^3 \text{ g}^{-1}$ ). The pore diameter (Kernel:  $\text{N}_2$  on carbon at 77 K, sphere/cylindrical pores, adsorption branch, fitting error: 1.033%) was slightly decreased ( $d_{\text{pore,max}} = 1.22 \text{ nm}$ ), as well as the microporous surface fraction (67%).

Finally, for **D-PTO 3** again an increase in specific surface area ( $\text{SA}_{\text{BET}} = 677 \text{ m}^2 \text{ g}^{-1}$ ) was measured and a similar pore

Table 1 Nitrogen sorption data (77 K) of the **D-PTO** materials

#	Sample	$T_{\text{decomp}}^a$ [°C]	$\text{SA}_{\text{BET}}^b$ [ $\text{m}^2 \text{ g}^{-1}$ ]	$\text{SA}_{\text{Langmuir}}^b$ [ $\text{m}^2 \text{ g}^{-1}$ ]	$d_{\text{pore,max}}^b$ [nm]	$V_{\text{Pore}}^b$ [ $\text{cm}^3 \text{ g}^{-1}$ ]	$V_{\text{mikro}}^c$ [ $\text{cm}^3 \text{ g}^{-1}$ ]	$S_{\text{mikro}}^d$ [%]
1	<b>D-PTO-1</b>	285	290	333	0.67	0.187	0.070	59
2	<b>D-PTO-2a</b>	n.d.	472	531	1.27	0.264	0.136	71
3	<b>D-PTO-2b</b>	301	537	612	1.22	0.306	0.146	67
4	<b>D-PTO-3</b>	312	676	767	1.26	0.325	0.219	78

<sup>a</sup> Decomposition temperature determined by TGA under  $\text{N}_2$  atmosphere with  $10 \text{ K min}^{-1}$ . <sup>b</sup> Determined by QS-DFT (Kernel:  $\text{N}_2$  on carbon at 77 K, sphere/cylindrical pores). <sup>c</sup> Determined by *t*-plot method. <sup>d</sup> Determined by *t*-plot method as  $(\text{SA}_{\text{micro}}/\text{SA}_{\text{BET}}) \times 100$ .



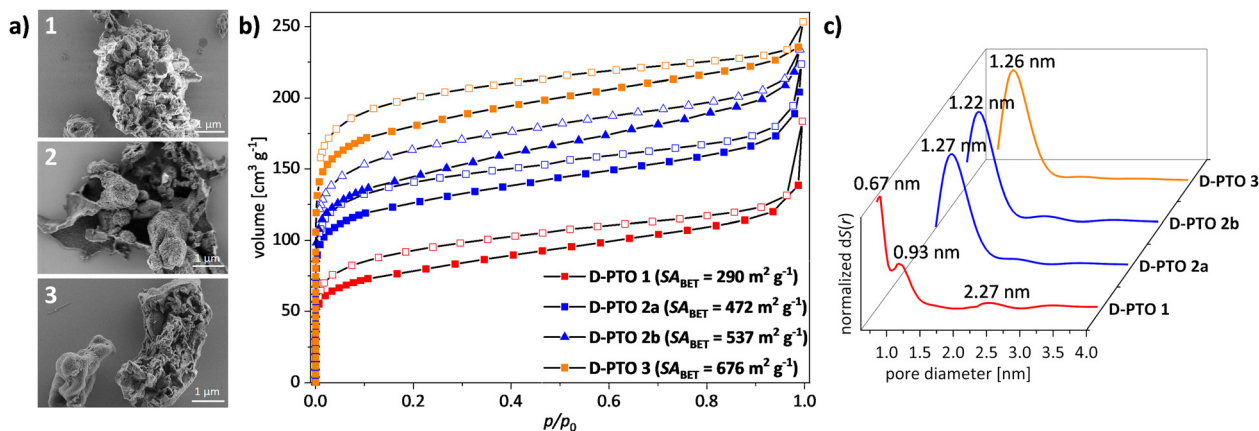



Fig. 5 (a) SEM images of **D-PTO-1**, **-2a**, and **-3** (from top to bottom). (b) BET gas sorption isotherms (N<sub>2</sub>, 77 K, vector dosing) after activation at 120 °C for 12 h. (c) pore size distribution (QSDFT, Kernel: N<sub>2</sub> on carbon at 77 K, sphere/cylindrical pore).

diameter as **D-PTOs 2a** and **2b** ( $d_{\text{pore,max}} = 1.26$  nm) was found (Kernel: N<sub>2</sub> on carbon at 77 K, sphere/cylindrical pores, adsorption branch, fitting error: 1.486%). The material shows the highest microporous pore volume ( $V_{\text{pore,micro}} = 0.219$  cm³ g⁻¹) and surface fraction (78%) of all materials presented at hand. On first glance, these findings indicate that reducing catalyst loading improves the surface properties in terms of higher specific surface area, larger pore volume and microporous fractions. However, in control experiments batch-to-batch variations occur, depending on the overall experimental conditions. Table 1 summarizes the gas sorption data.

### Electrochemical characterization and battery studies of the solid state D-PTO electrodes

In pyrene-tetraone-based cathode materials the carbonyl groups provide redox active sites for Li-ion storage, each of which can take up one electron upon reduction to adopt an anionic state that is balanced by a Li-cation.<sup>8</sup> The process is chemically reversible as the reduced oxy units can release electrons as well as the Li-ions and return to the neutral state (Scheme 3).

Assuming that each carbonyl unit can uptake one electron, the maximum capacity of **PTO** is 409 mA h g⁻¹, whereas 360 mA h g⁻¹ were achieved experimentally by Liang *et al.*<sup>8</sup> Due to its slightly higher molecular weight, the theoretical maximum capacity of **D-PTO** is 345 mA h g⁻¹. Electrodes were fabricated from **D-PTO-2a**, **-2b** and **-3** (see the ESI† for details)

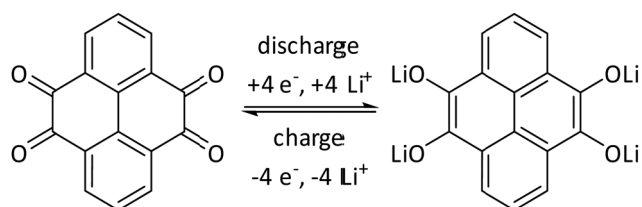

Scheme 3 Redox mechanism of pyrene tetraone.<sup>8</sup>

and electrochemical studies were performed using Swagelok-type two-electrode cells.<sup>47</sup>

2-Electrode half-cell cyclic voltammograms were recorded in a potential range between 1.5 and 4 V (4.5 V in case of **D-PTO-3**) (Fig. 6). The cyclic voltammogram of the composite electrode of **D-PTO-2a** shows two clear redox pairs located at 2.42 and 2.85 V vs. Li/Li⁺, with overpotentials of 0.1 and 0.02 V, respectively (Fig. 6a). This indicates a two-step redox process, similar to what is found in the CVs on model compound **2** (see Fig. 2).

The redox pair at 2.8 V splits into a two-step process after the first cycle, indicating changes of electrochemical properties at the polymer-carbon interface. Similarly, for **D-PTO-2b** two pairs of separated redox peaks are observed as well (Fig. 6b). The intensity of the redox peaks decreases upon cycling, which indicates degradation of the redox active sites. The origin of this degradation is unclear, especially since it is occurring only for **D-PTO-2b** and not with **D-PTO-2a**. At the same time, for both materials the overpotential of the redox pair decreases to approximately 0.1 V after the first cycle. This might be rationalized by a conformational rearrangement of the dendritic structure during the first cycle, which increases  $\pi$ -stacking between **D-PTO** and carbon black and thus improves bulk conductivity.

The oxidation peak at 3.8 V and reduction peak at 1.5 V are consistent with the redox activity observed in the precursor dendrimer **D-PTK**. Traces of residual tetraketone units, arising from incomplete hydrolysis in the second step of the synthesis (see Scheme 1) have already been observed in the solid state <sup>13</sup>C NMR spectroscopy (Fig. 4) and can thus be expected to be seen in the CVs as well. For **D-PTO-3** only one highly reversible redox peak pair at 2.8 V with a low overpotential of 0.05 V is found (Fig. 6c). During cycling the oxidation peak splits into two signals similar to what is observed for the other two materials.

The charge and discharge curves of the **D-PTO** composite electrodes were obtained at a current density of 100 mA g⁻¹ in the potential range between 1.5 V (for **D-PTO-3** 1.7 V) and 4 V (Fig. 6d-f). **D-PTO-2a** shows discharge plateaus at 2.3 V and 2.9 V vs. Li/Li⁺, which corresponds well with the reduction




Table 2 summarizes the main parameters describing the electrochemical performance of the composite electrode in Li-ion half-cells. The **D-PTO-2a** electrode exhibits the best performance overall, especially regarding the cycling stability seen in

	D-PTO-2a	D-PTO-2b	D-PTO-3
$C_{\text{spec,max}}^a$ [mA h g <sup>-1</sup> ]	137	115	143
Retention <sup>b</sup> [%]	86	41	70
Carbonyl utilization <sup>c</sup> [%]	40	33	41

The cycling stability of **D-PTO-2a** was further investigated by a long-term galvanostatic cycling measurement at 100 mA g<sup>-1</sup> for 130 cycles (Fig. 7a). Similar to what is observed in Fig. 6d, the specific discharge capacity initially increases before starting to fade after cycle 10 (*cf.* Fig. 6d). In addition, the data imply moderate fading for the subsequent 90 cycles before a rather

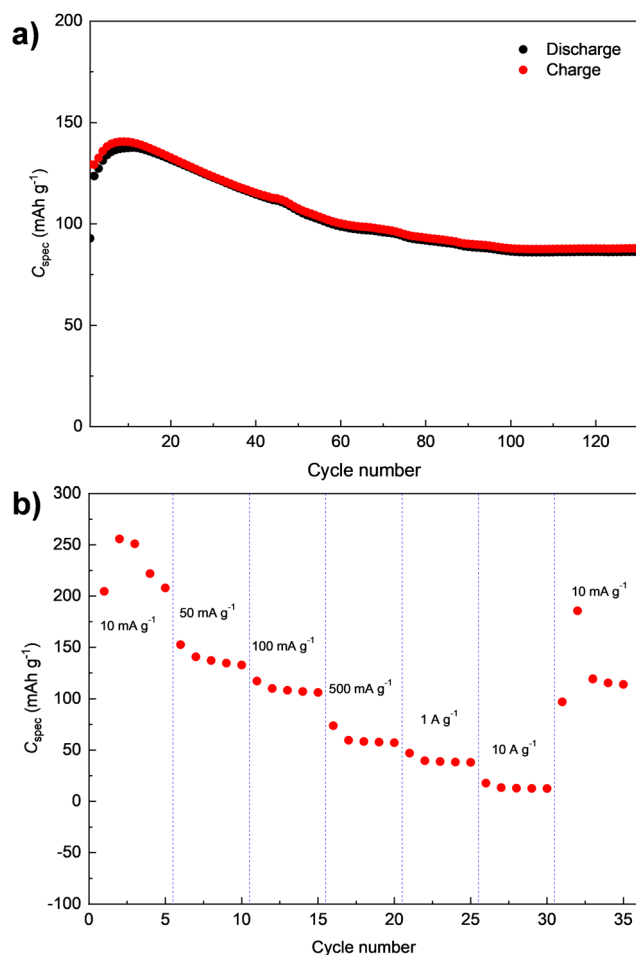


Fig. 7 Electrochemical performance of **D-PTO-2a** based composite electrodes within the potential range of 1.5–4 V (vs. Li/Li<sup>+</sup>): (a) cycling performance at 100 mA g<sup>−1</sup>. (b) Rate performance at various current densities.

stable capacity level is reached. Even after 130 cycles, a discharge capacity of 86 mA h g<sup>−1</sup> is measured, which corresponds to a capacity retention of 70% relative to the second cycle. The results of the corresponding rate capability test for **D-PTO-2a** are shown in Fig. 7b. The material delivers average capacities of 225, 140, 110, 52, 41, and 15 mA h g<sup>−1</sup> at current densities of 10,

50, 100, 500, 1000 and 10 000 mA g<sup>−1</sup>, respectively (Fig. 7b). A recovered capacity of 120 mA h g<sup>−1</sup> is achieved when the current density is reverted back to 10 mA g<sup>−1</sup>.

To relate the electrochemical performance of the here presented **D-PTO-2a** to the literature, Table 3 lists the electrochemical performances of various organic cathode materials. The comparison clearly shows that the **D-PTO-2a** competes well with different quinones as well as other redox-active polymers as it exhibits comparable initial discharge capacity and retention after 50 cycles.

## Conclusion

Redox active, insoluble pyrene tetraone dendrimers have been synthesized *via* a two-step synthesis route of Suzuki–Miyaura cross coupling of the borylated precursor **3** followed by acidic hydrolysis.

The prepared amorphous materials show BET surfaces between 290 and 676 m<sup>2</sup> g<sup>−1</sup>. The materials were used to fabricate composite electrodes, which were investigated regarding their electrochemical performance in lithium-ion secondary batteries. Specific capacities of up to 137 mA h g<sup>−1</sup> and a capacity retention of 86% after 50 cycles were measured. Moreover, favorable kinetics with high reversibility of the redox processes were observed. The results show that connecting the **PTO** monomers *via* the *meta*-positions of a benzene unit is a successful strategy to overcome the dissolution issue of **PTO**. The cycling stability of the as-prepared **D-PTO** is significantly improved compared to **PTO**.<sup>8</sup> In comparison to most other **PTO**-based materials (Scheme 1) the as-prepared **D-PTO** is also more cycle stable. Only the **PPYT** prepared by Yoshida and coworkers by attaching the **PTO** to a polymethacrylate backbone *via* an amide linkage, exhibits even higher cycling stability.<sup>12</sup> However, the low carbonyl utilization of only 40% still leaves room for improvement of the specific capacity.

## Conflicts of interest

There are no conflicts to declare.

Table 3 Comparison of the electrochemical performance of **D-PTO** with other organic cathodes as reported in the literature

Group	Material	Potential range vs. Li/Li <sup>+</sup> (V)	Current density (mA h g <sup>−1</sup> )	Initial discharge capacity (mA h g <sup>−1</sup> )	Retention/cycle no.	Ref.
Quinones	<b>D-PTO</b>	1.5–4.0	100	137	86%/50	This work
	<b>PPYT</b>	1.5–3.5	263	231	94%*/50	8
	<b>PYT-C</b>	1.5–3.4	74	123	65%*/50	9
	<b>PPTO</b>	1.5–3.5	100	234	74%/47	10
Imides	<b>PTCDA-HP</b>	1.5–3.5	110	130	84%/50	15
Carbonyl derivatives	<b>N-Cyanamide</b>	1.8–3.2	207	137	89%*/50	20
Thioether	<b>PPDT</b>	1.4–4.0	50	180	70%/20	31
Triphenylamines	<b>PPT1N</b>	2.6–4.5	20	129	91%/50	39
TEMPO	<b>PTMA</b>	3.0–4.0	111	133	90%*/50	43

Values marked with \*are read off from the graphs.



## Acknowledgements

The authors are grateful to Deutsche Forschungsgemeinschaft supporting this project (within the collaborative research center SFB1249 “N-heteropolycyclic compounds as functional materials” (TP-A04, TP-B02 and TP-B05).

## Notes and references

- 1 Press release: The Nobel Prize in Chemistry, 2019.
- 2 M. Kotal, S. Jakhar, S. Roy and H. K. Sharma, *J. Energy Storage*, 2022, **47**, 103534.
- 3 Y. Liang, Z. Tao and J. Chen, *Adv. Energy Mater.*, 2012, **2**, 742–769.
- 4 Z. Song and H. Zhou, *Energy Environ. Sci.*, 2013, **6**, 2280–2301.
- 5 L. Kong, M. Zhong, W. Shuang, Y. Xu and X.-H. Bu, *Chem. Soc. Rev.*, 2020, **49**, 2378–2407.
- 6 H. Lyu, X.-G. Sun and S. Dai, *Adv. Energy Sustainability Res.*, 2021, **2**, 2000044.
- 7 Z. Song, H. Zhan and Y. Zhou, *Angew. Chem., Int. Ed.*, 2010, **49**, 8444–8448.
- 8 Y. Liang, P. Zhang and J. Chen, *Chem. Sci.*, 2013, **4**, 1330–1337.
- 9 B. Häupler, A. Wild and U. S. Schubert, *Adv. Energy Mater.*, 2015, **5**, 1402034.
- 10 X. Han, C. Chang, L. Yuan, T. Sun and J. Sun, *Adv. Mater.*, 2007, **19**, 1616–1621.
- 11 S. Renault, J. Geng, F. Dolhem and P. Poizot, *Chem. Commun.*, 2011, **47**, 2414–2416.
- 12 T. Nokami, T. Matsuo, Y. Inatomi, N. Hojo, T. Tsukagoshi, H. Yoshizawa, A. Shimizu, H. Kuramoto, K. Komae, H. Tsuyama and J.-i. Yoshida, *J. Am. Chem. Soc.*, 2012, **134**, 19694–19700.
- 13 A. Jaffe, A. Saldivar Valdes and H. I. Karunadasa, *Chem. Mater.*, 2015, **27**, 3568–3571.
- 14 D. Chen, A.-J. Avestro, Z. Chen, J. Sun, S. Wang, M. Xiao, Z. Erno, M. M. Algaradah, M. S. Nassar, K. Amine, Y. Meng and J. F. Stoddart, *Adv. Mater.*, 2015, **27**, 2907–2912.
- 15 S. K. M. Nalluri, Z. Liu, Y. Wu, K. R. Hermann, A. Samanta, D. J. Kim, M. D. Krzyaniak, M. R. Wasielewski and J. F. Stoddart, *J. Am. Chem. Soc.*, 2016, **138**, 5968–5977.
- 16 Z. Luo, L. Liu, Q. Zhao, F. Li and J. Chen, *Angew. Chem., Int. Ed.*, 2017, **56**, 12561–12565.
- 17 D. J. Kim, K. R. Hermann, A. Prokofjevs, M. T. Otley, C. Pezzato, M. Owczarek and J. F. Stoddart, *J. Am. Chem. Soc.*, 2017, **139**, 6635–6643.
- 18 J. Xie, W. Chen, G. Long, W. Gao, Z. J. Xu, M. Liu and Q. Zhang, *J. Mater. Chem. A*, 2018, **6**, 12985–12991.
- 19 Y. Lu, X. Hou, L. Miao, L. Li, R. Shi, L. Liu and J. Chen, *Angew. Chem., Int. Ed.*, 2019, **58**, 7020–7024.
- 20 C.-J. Yao, Z. Wu, J. Xie, F. Yu, W. Guo, Z. J. Xu, D.-S. Li, S. Zhang and Q. Zhang, *ChemSusChem*, 2020, **13**, 2457–2463.
- 21 S. Lei, Y. Dong, Y. Dou, X. Zhang, Q. Zhang and Y. Yang, *Mater. Adv.*, 2021, **2**, 5785–5790.
- 22 X. Liu, S. Qiu, P. Mei, Q. Zhang and Y. Yang, *J. Mater. Sci.*, 2021, **56**, 3900–3910.
- 23 K. Oyaizu and H. Nishide, *Adv. Mater.*, 2009, **21**, 2339–2344.
- 24 T. Janoschka, M. D. Hager and U. S. Schubert, *Adv. Mater.*, 2012, **24**, 6397–6409.
- 25 K. Nakahara, K. Oyaizu and H. Nishide, *Chem. Lett.*, 2011, **40**, 222–227.
- 26 N. Oyama, T. Tatsuma, T. Sato and T. Sotomura, *Nature*, 1995, **373**, 598–600.
- 27 S.-R. Deng, L.-B. Kong, G.-Q. Hu, T. Wu, D. Li, Y.-H. Zhou and Z.-Y. Li, *Electrochim. Acta*, 2006, **51**, 2589–2593.
- 28 S. Zheng, D. Shi, D. Yan, Q. Wang, T. Sun, T. Ma, L. Li, D. He, Z. Tao and J. Chen, *Angew. Chem., Int. Ed.*, 2022, **61**, e202117511.
- 29 X.-X. Luo, W.-H. Li, H.-J. Liang, H.-X. Zhang, K.-D. Du, X.-T. Wang, X.-F. Liu, J.-P. Zhang and X.-L. Wu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202117661.
- 30 G.-P. Yang, X.-X. Luo, Y.-F. Liu, K. Li and X.-L. Wu, *ACS Appl. Mater. Interfaces*, 2021, **13**, 46902–46908.
- 31 M. Nagarathinam, K. Saravanan, E. J. H. Phua, M. V. Reddy, B. V. R. Chowdari and J. J. Vittal, *Angew. Chem., Int. Ed.*, 2012, **51**, 5866–5870.
- 32 K. Wada, K. Sakaushi, S. Sasaki and H. Nishihara, *Angew. Chem., Int. Ed.*, 2018, **57**, 8886–8890.
- 33 S. Gu, Z. Bai, S. Majumder, B. Huang and G. Chen, *J. Power Sources*, 2019, **429**, 22–29.
- 34 K. Zhang, T. H. Lee, B. Bubach, M. Ostadhassan, H. W. Jang, J.-W. Choi and M. Shokouhimehr, *RSC Adv.*, 2019, **9**, 21363–21370.
- 35 S.-Y. Li, W.-H. Li, X.-L. Wu, Y. Tian, J. Yue and G. Zhu, *Chem. Sci.*, 2019, **10**, 7695–7701.
- 36 S. Haldar, K. Roy, S. Nandi, D. Chakraborty, D. Puthusseri, Y. Gawli, S. Ogale and R. Vaidhyanathan, *Adv. Energy Mater.*, 2018, **8**, 1702170.
- 37 C. R. DeBlase, K. Hernández-Burgos, K. E. Silberstein, G. G. Rodríguez-Calero, R. P. Bisbey, H. D. Abruña and W. R. Dichtel, *ACS Nano*, 2015, **9**, 3178–3183.
- 38 S. Wang, Q. Wang, P. Shao, Y. Han, X. Gao, L. Ma, S. Yuan, X. Ma, J. Zhou, X. Feng and B. Wang, *J. Am. Chem. Soc.*, 2017, **139**, 4258–4261.
- 39 J. Merz, M. Dietz, Y. Vonhausen, F. Wöber, A. Friedrich, D. Sieh, I. Krummenacher, H. Braunschweig, M. Moos, M. Holzapfel, C. Lambert and T. B. Marder, *Chem. – Eur. J.*, 2020, **26**, 438–453.
- 40 L. Ueberricke, D. Mizioch, F. Rominger and M. Mastalerz, *Eur. J. Org. Chem.*, 2021, 4816–4823.
- 41 S. Brunauer, P. H. Emmett and E. Teller, *J. Am. Chem. Soc.*, 1938, **60**, 309–319.
- 42 A. V. Neimark, Y. Lin, P. I. Ravikovitch and M. Thommes, *Carbon*, 2009, **47**, 1617–1628.
- 43 G. Y. Gor, M. Thommes, K. A. Cychosz and A. V. Neimark, *Carbon*, 2012, **50**, 1583–1590.
- 44 G. Halsey, *J. Chem. Phys.*, 1948, **16**, 931–937.
- 45 J. H. de Boer, B. G. Linsen and T. J. Osinga, *J. Catal.*, 1965, **4**, 643–648.
- 46 J. H. de Boer, B. G. Linsen, T. van der Plas and G. J. Zondervan, *J. Catal.*, 1965, **4**, 649–653.
- 47 C. Jähne, C. Neef, C. Koo, H.-P. Meyer and R. Klingeler, *J. Mater. Chem. A*, 2013, **1**, 2856–2862.

