



Cite this: *Polym. Chem.*, 2023, **14**, 2662

Received 7th March 2023,  
Accepted 5th May 2023

DOI: 10.1039/d3py00248a

rsc.li/polymers

## Thermoresponsive polymer brush photocatalytic substrates for wastewater remediation†

Kirsten Bell,<sup>a</sup> Yiwen Guo,<sup>a</sup> Samuel Barker,<sup>a</sup> Seong H. Kim<sup>a,b,c</sup> and Christian W. Pester<sup>a</sup> \*<sup>a,b,c</sup>

Synthesis and characterization of a multi-responsive micron-scale heterogeneous catalyst are described. The temperature-responsive monomer *N*-isopropylacrylamide (NIPAAm) is copolymerized with the photo-active dye fluorescein *o*-acrylate (FIA) via surface-initiated reversible addition–fragmentation chain transfer (SI-RAFT) polymerization at varying thicknesses (*i.e.*, molecular weights). The resulting poly(FIA-*co*-NIPAAm) copolymer brushes were found to undergo a rapid structural change between 24 and 26 °C, which significantly alters the photocatalytic behavior of the incorporated fluorescein. A wastewater treatment application was implemented to study the effect between temperature and film thickness. Notably, increasing the reaction temperature above the lower critical solution temperature (LCST) increased the performance in the degradation of tetracycline hydrochloride (TC) with the thickest of the photocatalyst polymer brushes showing the most pronounced temperature response.

### Introduction

Increasing human population and global water shortage steadily augment the demand for continuous freshwater supply and wastewater remediation.<sup>1–3</sup> Amongst man-made water contaminants are pharmaceuticals, cosmetics, and personal care products, which are discarded into the natural environment during their manufacturing, after their use, or upon disposal.<sup>4–8</sup> Growing evidence regarding their deleterious effects on human health and the environment spawn increasing efforts for alternative and efficient wastewater treatment approaches.<sup>5,9–12</sup> Solutions include membranes, advanced oxi-

dation processes, precipitation, adsorption, or the conventional activated sludge treatment.<sup>13–16</sup>

Photocatalysis has been explored as a viable option to leverage ultraviolet (UV) or visible light – as naturally abundant from the sun – to drive degradation of toxic chemicals and pharmaceuticals into harmless, small substances.<sup>16–19</sup> Examples include the degradation of textile dyes, such as Rhodamine B and Methylene Blue, petroleum hydrocarbons, phenolic compounds, or the removal of heavy metal ions, antibiotics, pesticides, and other contaminants.<sup>14</sup>

While potent, transition metal and organic photocatalysts bear significant limitations that hinder their widespread adoption in wastewater treatment. Amongst these are (i) their expensive nature, (ii) limited solubility in aqueous media due to their aromatic skeletons, and (iii) challenges in their separation from the treated water.<sup>20</sup> These constraints have motivated research into heterogeneous photocatalysts, which has become the most broadly studied method to leverage photocatalysts in wastewater treatment.<sup>13,14,16,17,20,21</sup> For example, metal oxides (*e.g.* TiO<sub>2</sub> or ZnO) composite photocatalysts have been extensively studied as in the removal of pollutants.<sup>22–30</sup> These heterogeneous photocatalysts require high energy in the ultraviolet region to overcome a large band gap or complex synthetic route to increase their stability.<sup>21</sup> In addition, such metal-based photocatalysts can contaminate the water treatment process, depending on their retrieval and separation method as well as corrode in an aqueous environment.<sup>31,32</sup> Alternative approaches include nanoparticles,<sup>22</sup> polymer networks,<sup>33</sup> or metal organic frameworks<sup>24</sup> (MOFs), which lead to complex separation and recovery steps and decrease recyclability efficiency.

Multi-responsive photoactive polymers are an intriguing and effective approach towards photocatalysis.<sup>20,34,35</sup> Such systems provide tunable photocatalytic activity in response to a second stimulus – *e.g.*, pH,<sup>36</sup> addition of CO<sub>2</sub>,<sup>37</sup> or temperature<sup>38</sup> – which expands and/or contracts the catalyst-surrounding matrix or modifies its chemical environment. Proof-of-concept studies exist on how the activity of a network-incorporated photocatalyst can be modulated by modifying steric

<sup>a</sup>Department of Chemical Engineering, The Pennsylvania State University, University Park, PA 16802, USA. E-mail: pester@psu.edu

<sup>b</sup>Department of Materials Science and Engineering, The Pennsylvania State University, University Park, PA 16802, USA

<sup>c</sup>Department of Chemistry, The Pennsylvania State University, University Park, PA 16802, USA

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3py00248a>



**Fig. 1** Illustration of the overall idea of combining both thermal and light responsive features on a surface.

access to the active sites through external stimuli.<sup>33,39–44</sup> Despite their promise, only a few limited examples of multi-responsive organic heterocatalytic photoactive materials exist.<sup>43,45</sup> Their limitations include inadequate solubility<sup>46,47</sup> or limited synthetic versatility. For polymer-based photocatalysts, separating a synthetic product the photocatalytic polymer often remains prohibitively challenging.

Here, we attempt to address these limitations by engineering a dual responsive heterogeneous photocatalyst (temperature and light) based on photocatalytic polymer brushes (Fig. 1) that provides tunable photocatalytic properties while allowing facile separation from the reaction mixture. In detail, *N*-isopropylacrylamide (NIPAAm) is copolymerized with the photoactive fluorescein *o*-acrylate (FIA) to produce a multi-responsive smart material poly(FIA-*co*-NIPAAm) (Fig. 2a). Poly(*N*-isopropylacrylamide) (PNIPAAm) homopolymers are well-known to undergo a change from intramolecular (hydrophilic) to intermolecular (hydrophobic) interactions in H<sub>2</sub>O at a lower critical solution temperature ( $T_{LCST,avg} = 32$  °C). The LCST of

poly(NIPAAm) and its copolymers has been shown to vary based on molecular weight, concentration, composition, and various other parameters.<sup>48</sup> This was leveraged previously to produce thermoresponsive materials, coatings, and surface-tethered macromolecules (polymer brushes) that show well-controlled temperature response.<sup>49–54</sup> PNIPAAm is commonly studied in biomedical applications<sup>48,55–58</sup> or membrane filtration,<sup>59,60</sup> but there has also been interest in its use for wastewater treatment.<sup>61</sup> The described approach provides facile functionalization of inexpensive and optically transparent materials (glass beads) and the ability to tune photocatalytic activity *via* temperature. The resulting heterogeneous photocatalysts can easily be filtered off and separated from the reaction medium. A model degradation of tetracycline hydrochloride (TC) is studied to highlight utility of these materials in wastewater remediation and examine their dual reactivity. TC is a common antibiotic pollutant in aqueous systems.<sup>62,63</sup> While other groups have shown PNIPAAm/photocatalyst systems that generally decrease their activity upon heating, our studies surprisingly show increasing TC degradation at elevated temperatures above the material's LCST.

## Results and discussion

### Synthesis of dual responsive substrates

The synthesis of dual responsive polymer brush photocatalytic materials was performed following our previously published surface-initiated reversible addition-fragmentation chain transfer (SI-RAFT) polymerization approach (see ESI†).<sup>64,65</sup> The



**Fig. 2** (a) Illustration of the dual-responsive poly(fluorescein *o*-acrylate-*co*-*N*-isopropylacrylamide) heterogeneous catalysts and (b) comparing the experimental molecular weights from the free polymer formed in solution to increasing the thickness of poly(FIA-*co*-NIPAAm) on silicon wafers. Note, the cartoon is not drawn to scale as the polymer brushes are on the nanoscale. Surface functionalization of FN@SiO<sub>x</sub> confirmed through (c) X-ray photoelectron spectroscopy (XPS) and an example high resolution carbon C 1s spectrum for FN@SiO<sub>x</sub>-15 nm coating, and (d) ultraviolet-visible diffuse reflectance (UV/vis DR) spectroscopy for the varying thicknesses.

**Table 1** Summary of the varying film thicknesses and their respective water contact angle (WCA) for the dual responsive polymer brushes

Entry	Experimental conditions <sup>a</sup> [NIPAAm]:[FLA]:[CDTPA]	Thickness <sup>b</sup> ( <i>d</i> , nm)	Water contact angle ( $\theta$ , °) <sup>c</sup>	$M_n$ <sup>d</sup> (g mol <sup>-1</sup> )	FLA incorporation
1 FN@SiO <sub>x</sub> -5	[250]:[25]:[1]	7.5 ± 0.03	65.2 ± 2.8	7000	13%
2 FN@SiO <sub>x</sub> -15	[500]:[50]:[1]	13.1 ± 0.4	65.8 ± 1.2	13 000	13%
3 FN@SiO <sub>x</sub> -25	[1000]:[100]:[1]	22.9 ± 0.5	64.8 ± 1.1	22 900	9%
4 <sup>e</sup> PNIPAAm	[1000]:[0]:[1]	24.3 ± 1.8	55.6 ± 0.6	16 700	—
5 PFLA	[0]:[100]:[1]	10.8 ± 1.2	46.6 ± 3.4	12 700	100%

<sup>a</sup> NIPAAm = *N*-isopropylacrylamide, FLA = fluorescein *o*-acrylate, CDTPA = 4-cyano-4-[(dodecylsulfanylthiocarbonyl)sulfanyl] pentanoic acid. The thermal SI RAFT polymerization was carried out in inert atmosphere with ABIN (0.25 molar ratio) as initiator at 75 °C for 24 hours in DMF. The wafers were cleaned with DCM and MeOH, followed by a stream of nitrogen. <sup>b</sup> Thickness determined through J.A. Woollam RC2-D VASE. <sup>c</sup> WCA measurements determined *via* an in-house setup (Fig. S8†). <sup>d</sup> Molecular weight determined through chain-end analysis using <sup>1</sup>H NMR in DMSO-d<sub>6</sub>. <sup>e</sup> Pure PNIPAAm polymer brush wafer cleaned only with MeOH and molecular weight determined through chain end analysis using <sup>1</sup>H NMR in CDCl<sub>3</sub>.

RAFT chain transfer agent (CTA) 4-cyano-4-[(dodecylsulfanylthiocarbonyl)sulfanyl] pentanoic acid (CDTPA) was immobilized on soda lime silica (SiO<sub>x</sub>) glass beads ( $D_z = 76.3 \mu\text{m}$ ) to afford SI-RAFT of a thermoresponsive copolymer comprised of 10 mol% fluorescein *o*-acrylate (FLA) in *N*-isopropylacrylamide (NIPAAm) (see Fig. 2a). All SI-RAFT polymerizations were conducted in *N,N*-dimethylformamide (DMF) and initiated *via* 2,2'-azobis(isobutyronitrile) (AIBN).

Table 1 summarizes the synthesized photocatalytic materials. Poly(FLA-*co*-NIPAAm) polymer brushes (abbreviated as FN@SiO<sub>x</sub>) were synthesized at varying monomer to free CTA ratios to control the final polymer brush thickness on the SiO<sub>x</sub> surface. Free poly(FLA-*co*-NIPAAm) polymer simultaneously formed in solution were used to determine molecular weight ( $M_n$ ) and composition *via* nuclear magnetic resonance spectroscopy (<sup>1</sup>H NMR, Table 1, and Fig. S2–4†). Varying the molar ratio of NIPAAm to CDTPA allowed control over molecular weights. Good agreement was observed between the targeted and experimentally determined incorporation of FLA at an average of 11.7 mol% as determined by <sup>1</sup>H NMR (see Fig. S2†). At a feed ratio of 10 mol% in the polymerization mixture, fluorescein incorporation into the copolymer was slightly higher (13 mol%) at lower target molecular weights and decreased incorporation (just under at 9 mol%) at higher NIPAAm:CDTPA ratios. This can be attributed to mass transfer limitations observed by gelation of the reaction mixture at increasing target polymer molecular weights.

### Characterization of the dual responsive surfaces

To estimate thicknesses of the photocatalytic polymer brushes, SI-RAFT was performed simultaneously on both SiO<sub>x</sub> glass beads and planar substrates. Variable angle spectroscopic ellipsometry (VASE) was used to quantify the resulting FN@SiO<sub>x</sub> polymer brush thickness, *d*, for various [monomer]:[CTA] ratios (see Table 1). An average film of  $d \approx 7.5 \text{ nm}$  thickness was observed for molar ratio of [NIPAAm]:[FLA]:[CDTPA] of [250]:[25]:[1] (FN@SiO<sub>x</sub>-5 nm). Increasing the overall concentration of monomers resulted in an increased brush thickness of  $d \approx 22.9 \pm 0.5 \text{ nm}$  ([1000]:[100]:[1] or FN@SiO<sub>x</sub>-25 nm). Fig. 2b shows how the increase of FN@SiO<sub>x</sub> film thickness correlated with increasing

molecular weights of the poly(FLA-*co*-NIPAAm) copolymers formed in solution (Fig. 2b).

The resulting FN@SiO<sub>x</sub> glass beads and flat silicon wafers were characterized with X-ray photoelectron spectroscopy (XPS). Fig. 2c and Fig. S5 and 6† show survey and high-resolution scans of the C 1s carbon environment for FN@SiO<sub>x</sub> catalysts of varying thicknesses. Increasing polymer brush thickness was evidenced for both glass beads and silicon wafers through the decreasing intensity of the Si 2p silicon peak at BE = 102 eV (see survey spectra). In the case of the soda-lime beads, the Na KLL Auger peak at BE = 497 eV decreased with increasing copolymer brush film thickness. High resolution C 1s curve fits further verified individual carbon environments on all substrates: C–C (285 eV), C–(N,O) (286.4 eV), and both carbonyl C=O and amide N–C=O carbon atoms (288.0 eV). The nitrogen/carbon signal ratio (N 1s : C 1s) was used to elucidate the fluorescein *o*-acrylate incorporation. N 1s : C 1s ratios for the functionalized FN@SiO<sub>x</sub> beads were experimentally determined to 0.13, 0.13, and 0.12 for films of 5 nm, 15 nm, and 25 nm targeted thickness, respectively. This matches well with the anticipated ratio of N 1s : C 1s = 0.12 that was calculated based on a 10 mol% feed of fluorescein *o*-acrylate monomer (Table S2†). In addition, the similar nitrogen to carbon ratios confirmed the random copolymerization between the NIPAAm and FLA monomers.

The photoactive FN@SiO<sub>x</sub> films produced hydrophilic coatings (at room temperature) as apparent from their water contact angles ( $\theta$ , Fig. S9† and Table 1). The CDTPA initiating monolayer exhibited hydrophobic properties ( $\theta \approx 94.9 \pm 2.4^\circ$ ) prior to SI-RAFT polymerization. In comparison to pure PNIPAAm coatings ( $\theta \approx 55.6 \pm 0.6^\circ$ ) and a PFLA films ( $\theta \approx 46.6 \pm 3.4^\circ$ ) the copolymerized FN@SiO<sub>x</sub> polymer brushes exhibited a slightly increased hydrophobicity at  $\theta \approx 65.2 \pm 0.5^\circ$ . Notably, there was no appreciable water contact angle difference between the distinct film thicknesses.

Further, Fig. 2d shows how the overall concentration of fluorescein increases with FN@SiO<sub>x</sub> polymer brush film thickness as determined *via* ultraviolet-visible (UV/vis) diffuse reflectance (DR) spectroscopy. An emission spectrum was collected *via* multiphoton microscopy of FN@SiO<sub>x</sub> in H<sub>2</sub>O (Fig. S7†) to determine the fluorescence of the photocatalyst

when polymerized on a surface. When excited, the beads emitted fluorescence at  $\lambda_{\text{max}} = 500$  nm and an observed lifetime of 3.3 ns, which is comparable to reports on fluorescein as a small molecule in solution.<sup>66</sup> Consequently, copolymerizing fluorescein into a surface-tethered polymer appears to not significantly influence its photophysical properties.

### Thermoresponsive transition

The thermoresponsive behavior of the FN@SiO<sub>x</sub> photocatalytic polymer brush films in deionized water (DIW) was confirmed by monitoring, *in situ*, the film thickness as a function of solution with VASE and a heated liquid cell. Fig. 3a shows how the FN@SiO<sub>x</sub>-15 nm copolymer brush film thickness begins to decrease around 24 °C and plateaus above 26 °C, yielding a change of ~25% in film thickness (from  $d_0 = 14.1$  nm to  $d = 10.6$  nm). The pure PNIPAAm polymer brush ( $d_0 = 24.1$  nm) displayed a change in thickness over a temperature range from 26 °C to 32 °C to a final thickness of  $d = 12.1$  nm (Fig. 3a). As such, the addition of a hydrophobic fluorescein comonomer decreases the LCST from 28 °C to 25 °C. These findings agree with those of previous groups, where indeed the LCST of a PNIPAAm thin films and polymer brushes were found to be lower than in solution.<sup>53,54</sup> In contrast, the PFIA film control experiment did not show any temperature response and polymer brush thickness remained constant over the examined temperature range (Fig. 3a).

Vibrational sum frequency generation (SFG) spectroscopic analysis of the FN@SiO<sub>x</sub> films showed that the polymer brush surface undergoes substantial changes (Fig. 3b and Fig. S10†). The ratio of the 2878 cm<sup>-1</sup> peak in the *ssp* polarization spectrum to the 2970 cm<sup>-1</sup> peak in the *ppp* polarization spectrum is ~3.4 below LCST and becomes ~0.22 above LCST. This implies that CH<sub>3</sub> groups at the brush end are tilted about 35° from the surface normal when the brush is extended below LCST and reoriented nearly parallel to the surface when the

brush is collapsed above LCST.<sup>67</sup> Also, the -N(H)- and -OH groups appear to be nearly normal to the surface below LCST (strong in the *ssp* spectrum) and become more parallel to the surface above LCST (stronger in the *ppp* spectrum).

### Degradation of tetracycline hydrochloride (TC)


The efficacy of dual responsive FN@SiO<sub>x</sub> heterogeneous photocatalysts was evaluated by studying the light-mediated degradation of tetracycline hydrochloride (TC, see Fig. 4b inset for compound structure). TC is a commonly used antibiotic to treat acne and has been frequently detected in water resources.<sup>62,63</sup> TC is known to cause allergic reactions, exhibit non-specific toxicity in water, and, as an antibiotic, consistent prolonged exposure to TC can lead to the development of resistance and decreased efficiency in patients.<sup>11,62,63</sup>

Fig. 4a shows FN@SiO<sub>x</sub>-catalyzed TC degradation kinetics for the three distinct FN@SiO<sub>x</sub> polymer brush catalysts synthesized. UV/Vis spectroscopy was used to measure how [TC] concentration changes with time ( $C/C_0$ , see Fig. 4b for an example of raw UV/vis data). Experiments were performed by irradiating a solution of TC in deionized water (DIW) with white LEDs (Fig. S11 and S17† for irradiation of natural sunlight). To interrogate the influence of temperature, experiments were performed below LCST ( $T = 22$  °C) and at elevated temperature above LCST ( $T = 50$  °C, Fig. S11†). Before any data collection, the molar absorptivity coefficient was determined *via* a calibration curve of TC at varying concentrations ( $\epsilon = 1.62 \times 10^7$  M<sup>-1</sup> cm<sup>-1</sup> at  $\lambda = 356$  nm, Fig. S12†).

At room temperature ( $T < \text{LCST}$ ), little difference in degradation rates was observed between the photocatalytic brushes of different thicknesses (Fig. 4a). We found this surprising, considering that UV/vis DR spectroscopy (see Fig. 2d) clearly indicated an increased fluorescein concentration with the brush thickness. Approximately 50% of the TC is degraded after 2 hours of reaction time, corresponding to an average



**Fig. 3** (a) Determination of the lower critical solution temperature (LCST) for the dual-responsive poly(fluorescein *o*-acrylate-*co*-*N*-isopropylacrylamide) polymer brushes compared to only PNIPAAm and PFIA films in deionized water (DIW). (b) Sum frequency generation (SFG) spectra of the FN@SiO<sub>x</sub>-25 nm film at 22 °C and 40 °C in air with 70% relative humidity.

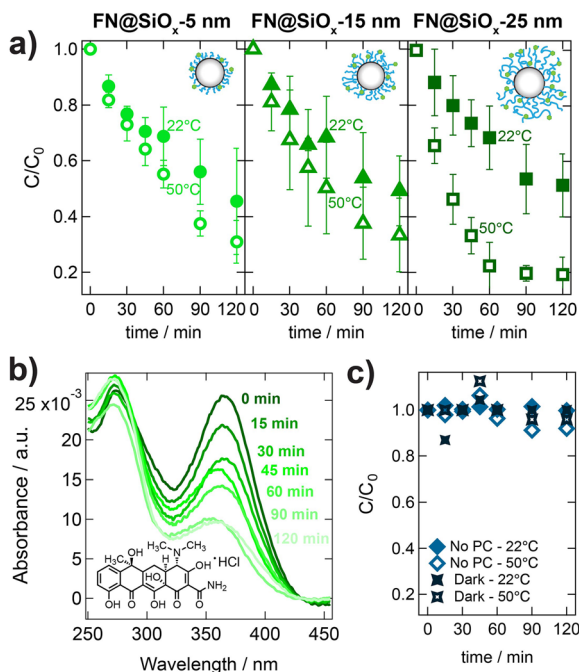

**Fig. 4** (a) Photocatalytic degradation of tetracycline hydrochloride (TC) kinetic performance of the different FN@SiO<sub>x</sub> heterogeneous dual-responsive catalysts at a temperature above and below the LCST. (b) Example raw UV/vis data for the degradation of TC with FN@SiO<sub>x</sub>-15 nm at room temperature with an inset of TC's molecular structure. (c) Control experiments attempting degradation of TC in the dark and absence of photocatalyst.

0.0065 min<sup>-1</sup> rate constant (*k*) as determined by a pseudo-first order reaction rate from ln(*C*/*C*<sub>0</sub>) with respect to time (*t*, Fig. S13 and Table S4†).

$$\ln\left(\frac{C}{C_0}\right) = kt. \quad (1)$$

In contrast, elevating the temperature to 50 °C, *i.e.*, above *T* > LCST, improves degradation rates for all catalysts (see Fig. S13 and Table S4† for summary of rate constants). Notably, thicker poly(FLA-*co*-NIPAAm) brushes lead to faster TC degradation rates (Fig. 4 and S13†). The catalytic efficiency increases from ~50% to ~68% for both FN@SiO<sub>x</sub>-5 nm and FN@SiO<sub>x</sub>-15 nm with an average of 0.0102 min<sup>-1</sup> rate constant. Interestingly, the thickest brush (FN@SiO<sub>x</sub>-25 nm) demonstrates the most response to temperature – while at room temperature it does not significantly stand out when compared to thinner photocatalytic films. For FN@SiO<sub>x</sub>-25 nm, the degradation of TC almost doubled in efficiency increasing from 49% (RT) to 81% (50 °C), with an increased 0.0175 min<sup>-1</sup> rate constant. This suggests a conformational rearrangement of the polymer brushes above LCST (Fig. 3b and Fig. S10†), which would affect the availability of fluorescein for photocatalysis either by being exposed at the outermost surface or the chain end conformations allowing more ingress of TC into the brush.

Control experiments in the absence of photocatalysts (but under irradiation) or in the dark showed no significant degradation of the TC antibiotics and negligible temperature effects or thermal degradation were observed (see Fig. 4c and Fig. S14†).

Based on these findings, the dual thermo- and photo-active heterogeneous catalysts show improved performance at elevated temperatures. We hypothesize that the conformational collapse of the PNIPAAm backbone above LCST leads to an increased accessibility of TC to the fluorescein photocatalysts. This would improve catalytic performance for all films but be most pronounced for thicker films. As such, this hypothesis aligns well with our experimental findings.

Notably, this result contrasts with previous work on thermo-responsive photocatalysis.<sup>68–71</sup> For example, Huo *et al.* used PNIPAM@AgBr/CSS nanocomposites for the degradation of tetracycline for a dual-responsive purpose. They found that above the LCST and higher temperatures, the degradation rate decreased.<sup>72</sup> In another multi-responsive study, Yoon *et al.* observed with a hybrid Au-PNIPAM film with ZnO nanoparticles, an increase in performance at elevated temperatures in the degradation of *p*-nitrophenol for thin films and low molecular weights.<sup>73</sup> However, at high molecular weights and thicker films they noticed a decrease in catalyst efficiency at a temperature above the LCST.<sup>73</sup> Initially, their studies are in agreement with our findings at FN@SiO<sub>x</sub>-5,15 nm; however, the higher molecular weight and thicker films are contrasting our investigation with a fully organic dual responsive heterogeneous catalyst.

Preliminary studies show similar results for other compounds in water remediation efforts. For the removal of the dye methylene blue (MB), FN@SiO<sub>x</sub>-25 nm degraded 79% of MB at room temperature (Fig. S18b†). The catalytic efficiency increased to 97% at elevated temperatures, which is complementary to what we are observing in the degradation of TC. Further studies are going towards the study of other substrates and whether this is a universal trend for different compounds.

We further tested the stability of the FN@SiO<sub>x</sub> substrates by recycling them in three consecutive degradations of TC at the two different temperatures (Fig. S16†). Recovery through simple filtration successfully allowed the reusability of FN@SiO<sub>x</sub>-25 nm beads with negligible difference in catalytic performance over each reaction cycle. While Mao *et al.* recycled their dual responsive nanoparticles (ZnPC-*g*-TiO<sub>2</sub>-*g*-PNIPAAm) in the removal of the dye Rhodamine B (RhoB) at room temperature for three cycles, their separation process included a high-speed centrifugation and elevated temperatures of 45 °C.<sup>69</sup> The size of our supports eliminates the time and effort it takes to recover the heterogeneous catalysts typically needed for such processes, increasing recyclability efficiency.

## Conclusions

We described the synthesis of a dual-responsive heterogeneous catalyst based on photocatalytic polymer brushes comprised of

thermo-responsive *N*-isopropylacrylamide (NIPAAm) and photo-active fluorescein *o*-acrylate (FlA). The resulting surface-tethered photoactive poly(FlA-*co*-NIPAAm) polymer brushes showed well-controlled temperature response in water, in agreement with LCST behavior. To highlight the utility of these materials in wastewater remediation, we examined their dual reactivity for a model degradation of tetracycline hydrochloride (TC). At room temperature ( $T < \text{LCST}$ ), little difference in degradation rates was observed between the photocatalytic brushes of different thicknesses. At  $T > \text{LCST}$ , degradation rates are improved for all catalysts and thicker poly(FlA-*co*-NIPAAm) brushes lead to higher TC degradation rates. Interestingly, the thickest brush demonstrated the most pronounced temperature response, while it does not significantly stand out when compared to thinner photocatalytic films at room temperature.

## Author contributions

All authors approved the final version of the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

C. W. P. acknowledges the National Science Foundation (NSF CBET Award # 2143628) for financial support. The authors would like to thank Dr T. J. Zimudzi (PSU Materials Characterization Lab) for assistance with obtaining UV/vis data, Winters Guo and Prof. Gina Noh for UV/vis DR support, Missy Hazen for fluorescence microscopy training, and Prof. Bryan Vogt and Minseo Kim for support with ellipsometry data collection and fitting. In addition, the authors would like to acknowledge Axalta for supporting the SFG data collection.

## References

- 1 J. Eliasson, *Nature*, 2015, **517**, 6.
- 2 J. E. Cohen, *Science*, 2003, **302**, 1172–1175.
- 3 H. Bigas, Water security and the global water agenda : a UN-water analytical brief, United Nations University - Institute for Water, Environment and Health, 2013.
- 4 Unesco, World Water Assessment Programme (United Nations), UN-Water Water and climate change.
- 5 J. L. Wilkinson, A. B. A. Boxall, D. W. Kolpin, K. M. Y. Leung, R. W. S. Lai, C. Galban-Malagon, A. D. Adell, J. Mondon, M. Metian, R. A. Marchant, A. Bouzas-Monroy, A. Cuni-Sanchez, A. Coors, P. Carriquiriborde, M. Rojo, C. Gordon, M. Cara, M. Moermond, T. Luarte, V. Petrosyan, Y. Perikhanyan, C. S. Mahon, C. J. McGurk, T. Hofmann, T. Kormoker, V. Iniguez, J. Guzman-Otazo, J. L. Tavares, F. Gildasio De Figueiredo, M. T. P. Razzolini, V. Dougnon, G. Gbaguidi, O. Traore, J. M. Blais, L. E. Kimpe, M. Wong, D. Wong, R. Ntchantcho, J. Pizarro, G.-G. Ying, C.-E. Chen, M. Paez, J. Martinez-Lara, J.-P. Otamonga, J. Pote, S. A. Ifo, P. Wilson, S. Echeverria-Saenz, N. Udikovic-Kolic, M. Milakovic, D. Fatta-Kassinis, L. Ioannou-Ttofa, V. Belusova, J. Vymazal, M. Cardenas-Bustamante, B. A. Kassa, J. Garric, A. Chaumot, P. Gibba, I. Kunchulia, S. Seidensticker, G. Lyberatos, H. P. Halldorsson, M. Melling, T. Shashidhar, M. Lamba, A. Nastiti, A. Supriatin, N. Pourang, A. Abedini, O. Abdullah, S. S. Gharbia, F. Pilla, B. Chefetz, T. Topaz, K. M. Yao, B. Aubakirova, R. Beisenova, L. Olaka, J. K. Mulu, P. Chatanga, V. Ntuli, N. T. Blama, S. Sherif, A. Z. Aris, L. J. Looi, M. Niang, S. T. Traore, R. Oldenkamp, O. Ogunbanwo, M. Ashfaq, M. Iqbal, Z. Abdeen, A. O'Dea, J. M. Morales-Saldana, M. Custodio, H. de la Cruz, I. Navarrete, F. Carvalho, A. B. Gogra, B. M. Koroma, V. Cerkenik-Flajs, M. Gombac, M. Thwala, K. Choi, H. Kang, J. L. C. Ladu, A. Rico, P. Amerasinghe, A. Sobek, G. Horlitz, A. K. Zenker, A. C. King, J.-J. Jiang, R. Kariuki, M. Tumbo, U. Tezel, T. T. Onay, J. B. Lejju, Y. Vystavna, Y. Vergeles, H. Heinzen, A. Perez-Parada, D. B. Sims, M. Figy, D. Good and C. Teta, *Proc. Natl. Acad. Sci. U. S. A.*, 2022, **119**, e2113947119.
- 6 T. aus der Beek, F. A. Weber, A. Bergmann, S. Hickmann, I. Ebert, A. Hein and A. Küster, *Environ. Toxicol. Chem.*, 2016, **35**, 823–835.
- 7 D. W. Kolpin, E. T. Furlong, M. T. Meyer, E. M. Thurman, S. D. Zaugg, L. B. Barber and H. T. Buxton, *Environ. Sci. Technol.*, 2002, **36**, 1202–1211.
- 8 A. B. A. Boxall, M. A. Rudd, B. W. Brooks, D. J. Caldwell, K. Choi, S. Hickmann, E. Innes, K. Ostapyk, J. P. Staveley, T. Verslycke, G. T. Ankley, K. F. Beazley, S. E. Belanger, J. P. Berninger, P. Carriquiriborde, A. Coors, P. C. DeLeo, S. D. Dyer, J. F. Ericson, F. Gagné, J. P. Giesy, T. Guoin, L. Hallstrom, M. v. Karlsson, D. G. Joakim Larsson, J. M. Lazorchak, F. Mastrocco, A. McLaughlin, M. E. McMaster, R. D. Meyerhoff, R. Moore, J. L. Parrott, J. R. Snape, R. Murray-Smith, M. R. Servos, P. K. Sibley, J. O. Straub, N. D. Szabo, E. Topp, G. R. Tetreault, V. L. Trudeau and G. van der Kraak, *Environ. Health Perspect.*, 2012, **120**, 1221–1229.
- 9 D. A. Gkika, A. C. Mitropoulos, D. A. Lambropoulou, I. K. Kalavrouziotis and G. Z. Kyzas, *Environ. Sci. Pollut. Res.*, 2022, **29**, 75223–75247.
- 10 K. A. Kidd, P. J. Blanchfield, K. H. Mills, V. P. Palace, R. E. Evans, J. M. Lazorchak and R. W. Flick, *Proc. Natl. Acad. Sci. U. S. A.*, 2017, **104**, 8897–8901.
- 11 E. M. H. Wellington, A. B. A. Boxall, P. Cross, E. J. Feil, W. H. Gaze, P. M. Hawkey, A. S. Johnson-Rollings, D. L. Jones, N. M. Lee, W. Otten, C. M. Thomas and A. P. Williams, *Lancet Infect. Dis.*, 2013, **12**, 155–165.
- 12 T. Brodin, J. Fick, M. Jonsson and J. Klaminder, *Science*, 2013, **339**, 814–815.

- 13 D. B. Miklos, C. Remy, M. Jekel, K. G. Linden, J. E. Drewes and U. Hübner, *Water Res.*, 2018, **139**, 118–131.
- 14 G. Ren, H. Han, Y. Wang, S. Liu, J. Zhao, X. Meng and Z. Li, *Nanomaterials*, 2021, **11**.
- 15 C. Grandclément, I. Seyssiecq, A. Piram, P. Wong-Wah-Chung, G. Vanot, N. Tiliacos, N. Roche and P. Doumenq, *Water Res.*, 2017, **111**, 297–317.
- 16 J. J. Rueda-Marquez, I. Levchuk, P. Fernández Ibañez and M. Sillanpää, *J. Cleaner Prod.*, 2020, **258**, 1–13.
- 17 A. Šuligoj, R. Cerc Korošec, G. Žerjav, N. Novak Tušar and U. Lavrenčič Štangar, *Top. Curr. Chem.*, 2022, **380**.
- 18 A. Shokri and M. Sanavi Fard, *Chem. Pap.*, 2022, **76**, 5309–5339.
- 19 S. N. Ahmed and W. Haider, *Nanotechnology*, 2018, **29**.
- 20 R. Li, K. Landfester and C. T. J. Ferguson, *Angew. Chem., Int. Ed.*, 2022, **61**, e202211132.
- 21 T. D. Nguyen, T. Lee, T. Van Tran, V. H. Nguyen, L. X. Nong, L. G. Bach and D. V. N. Vo, *Environ. Chem. Lett.*, 2023, **21**, 935–980.
- 22 N. Alhokbany, T. Ahamad and S. M. Alshehri, *J. Environ. Chem. Eng.*, 2022, **10**, 107681.
- 23 C. R. Chen, H. Y. Zeng, M. Y. Yi, G. F. Xiao, R. L. Zhu, X. J. Cao, S. G. Shen and J. W. Peng, *Ecotoxicol. Environ. Saf.*, 2019, **172**, 423–431.
- 24 M. Kaur, S. K. Mehta and S. K. Kansal, *Environ. Sci. Pollut. Res.*, 2023, **30**, 8464–8484.
- 25 W. Li, X. S. Chu, S. A. He, X. C. Wang and C. Y. Wang, *Environ. Sci.: Nano*, 2020, **7**, 2654–2668.
- 26 Y. N. Ren, W. Xu, L. X. Zhou and Y. Q. Zheng, *Polyhedron*, 2018, **139**, 63–72.
- 27 Y. N. Ren, W. Xu, Z. X. Si, L. X. Zhou and Y. Q. Zheng, *Polyhedron*, 2018, **152**, 195–201.
- 28 J. C. Shen, H. Y. Zeng, C. R. Chen and S. Xu, *Appl. Clay Sci.*, 2020, **185**, 105413.
- 29 W. Wang, J. Fang, S. Shao, M. Lai and C. Lu, *Appl. Catal., B*, 2017, **217**, 57–64.
- 30 H. Yang and J. Yang, *RSC Adv.*, 2018, **8**, 11921–11929.
- 31 B. Weng, M. Y. Qi, C. Han, Z. R. Tang and Y. J. Xu, *ACS Catal.*, 2019, **9**, 4642–4687.
- 32 S. I. S. Mashuri, M. L. Ibrahim, M. F. Kasim, M. S. Mastuli, U. Rashid, A. H. Abdullah, A. Islam, N. Asikin-Mijan, Y. H. Tan, N. Mansir, N. H. M. Kaus and T. Y. Y. Hin, *Catalysts*, 2020, **10**, 1–29.
- 33 F. Amir, X. Li, M. C. Gruschka, N. D. Colley, L. Li, R. Li, H. R. Linder, S. A. Sell and J. C. Barnes, *Chem. Sci.*, 2020, **11**, 10910–10920.
- 34 A. M. Urban, M. W. M. U. Urban, *Stimuli-Responsive Macromolecules and Polymeric Coatings*, ACS Symposium Series, 2005.
- 35 F. D. Jochum and P. Theato, *Chem. Soc. Rev.*, 2013, **42**, 7468–7483.
- 36 M. Chen, S. Deng, Y. Gu, J. Lin, M. J. MacLeod and J. A. Johnson, *J. Am. Chem. Soc.*, 2017, **139**, 2257–2266.
- 37 J. Byun, W. Huang, D. Wang, R. Li and K. A. I. Zhang, *Angew. Chem., Int. Ed.*, 2018, **57**, 2967–2971.
- 38 P. De, M. Li, S. R. Gondi and B. S. Sumerlin, *J. Am. Chem. Soc.*, 2008, **130**, 11288–11289.
- 39 C. T. J. Ferguson, N. Huber, K. Landfester and K. A. I. Zhang, *Angew. Chem., Int. Ed.*, 2019, **58**, 10567–10571.
- 40 J. Chen, M. Liu, H. Huang, F. Deng, L. Mao, Y. Wen, L. Huang, J. Tian, X. Zhang and Y. Wei, *J. Mol. Liq.*, 2018, **259**, 179–185.
- 41 P. Hernández, A. Lucero-Acuña, C. A. Gutiérrez-Valenzuela, R. Moreno and R. Esquivel, *E-Polymers*, 2017, **17**, 399–408.
- 42 D. Kamzabek, B. le Dé, L. Coche-Guérente, F. Miomandre and G. v. Dubacheva, *Langmuir*, 2021, **37**, 10971–10978.
- 43 R. A. Olson, J. S. Levi, G. M. Scheutz, J. J. Lessard, C. A. Figg, M. N. Kamat, K. B. Basso and B. S. Sumerlin, *Macromolecules*, 2021, **54**, 4880–4888.
- 44 J. J. Lessard, G. M. Scheutz, A. B. Korpusik, R. A. Olson, C. A. Figg and B. S. Sumerlin, *Polym. Chem.*, 2021, **12**, 2205–2209.
- 45 D. González-Muñoz, A. Gómez-Avilés, C. B. Molina, J. Bedia, C. Belver, J. Alemán and S. Cabrera, *J. Mater. Sci. Technol.*, 2022, **103**, 134–143.
- 46 D. J. Woods, R. S. Sprick, C. L. Smith, A. J. Cowan and A. I. Cooper, *Adv. Energy Mater.*, 2017, **7**, 1700479.
- 47 K. Stando, P. Kasprzyk, E. Felis and S. Bajkacz, *Molecules*, 2021, **26**, 7612.
- 48 T. Sarwan, P. Kumar, Y. E. Choonara and V. Pillay, *Front. Mater.*, 2020, **7**, 73.
- 49 S. Furyk, Y. Zhang, D. Ortiz-Acosta, P. S. Cremer and D. E. Bergbreiter, *J. Polym. Sci., Part A: Polym. Chem.*, 2006, **44**, 1492–1501.
- 50 X. Jia, X. Jiang, R. Liu and J. Yin, *Macromol. Chem. Phys.*, 2009, **210**, 1876–1882.
- 51 L. Liang, X. Feng, J. Liu and P. C. Rieke, *J. Appl. Polym. Sci.*, 1999, **72**, 1–11.
- 52 K. N. Plunkett, X. Zhu, J. S. Moore and D. E. Leckband, *Langmuir*, 2006, **22**, 4259–4266.
- 53 C. Xue, N. Yonet-Tanyeri, N. Brouette, M. Sferrazza, P. V. Braun and D. E. Leckband, *Langmuir*, 2011, **27**, 8810–8818.
- 54 Y. Yu, B. D. Kieviet, F. Liu, I. Siretanu, E. Kutnyánszky, G. J. Vancso and S. De Beer, *Soft Matter*, 2015, **11**, 8508–8516.
- 55 M. Sponchioni, U. Capasso Palmiero and D. Moscatelli, *Mater. Sci. Eng., C*, 2019, **102**, 589–605.
- 56 Y. J. Kim and Y. T. Matsunaga, *J. Mater. Chem. B*, 2017, **5**, 4307–4321.
- 57 C. Pietsch, U. S. Schubert and R. Hoogenboom, *Chem. Commun.*, 2011, **47**, 8750–8765.
- 58 M. A. Ward and T. K. Georgiou, *Polymers*, 2011, **3**, 1215–1242.
- 59 W. S. Ng, L. A. Connal, E. Forbes and G. V. Franks, *Miner. Eng.*, 2018, **123**, 144–159.
- 60 D. Xu, J. Zheng, X. Zhang, D. Lin, Q. Gao, X. Luo, X. Zhu, G. Li, H. Liang and B. Van der Bruggen, *Environ. Sci. Technol.*, 2022, **56**, 1927–1937.
- 61 X. Xu, N. Bizmark, K. S. S. Christie, S. S. Datta, Z. J. Ren and R. D. Priestley, *Macromolecules*, 2022, **55**, 1894–1909.

- 62 A. Javid, A. Mesdaghinia, S. Nasser, A. H. Mahvi, M. Alimohammadi and H. Gharibi, *J. Environ. Health Sci. Eng.*, 2016, **14**, 4.
- 63 P. T. P. Hoa, S. Managaki, N. Nakada, H. Takada, A. Shimizu, D. H. Anh, P. H. Viet and S. Suzuki, *Sci. Total Environ.*, 2011, **409**, 2894–2901.
- 64 K. Bell, S. Freeburne, A. Wolford and C. W. Pester, *Polym. Chem.*, 2022, **13**, 6120–6126.
- 65 K. Bell, S. Freeburne, M. Fromel, H. J. Oh and C. W. Pester, *J. Polym. Sci.*, 2021, **59**, 2844–2853.
- 66 A. S. Kristoffersen, S. R. Erga, B. Hamre and Ø. Frette, *J. Fluoresc.*, 2018, **28**, 1065–1073.
- 67 Y. T. Lin, M. Fromel, Y. Guo, R. Guest, J. Choi, Y. S. Li, H. Kaya, C. W. Pester and S. H. Kim, *Langmuir*, 2022, **38**, 14704–14711.
- 68 P. Huo, J. Li, Z. Ye, H. Wang, X. Liu, X. Li and Y. Yan, *Chin. Chem. Lett.*, 2017, **28**, 2259–2262.
- 69 B. Mao, C. Liu, X. Cui, Y. Li and Q. Duan, *Molecules*, 2022, **27**, 3330.
- 70 L. Sun, Y. Zhou, X. Li, J. Li, D. Shen, S. Yin, H. Wang, P. Huo and Y. Yan, *Chin. J. Catal.*, 2020, **41**, 1573–1588.
- 71 Z. Yu, D. Tang, H. Lv, Q. Feng, Q. Zhang, E. Jiang and Q. Wang, *Colloids Surf., A*, 2015, **471**, 117–123.
- 72 P. Huo, Z. Ye, H. Wang, Q. Guan and Y. Yan, *J. Alloys Compd.*, 2017, **696**, 701–710.
- 73 M. Yoon, J. E. Lee, Y. J. Jang, J. W. Lim, A. Rani and D. H. Kim, *ACS Appl. Mater. Interfaces*, 2015, **7**, 21073–21081.