

Journal of Materials Chemistry A

Materials for energy and sustainability

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Y. Lin, M. Liang and A. Eldeeb, *J. Mater. Chem. A*, 2025, DOI: 10.1039/D5TA06755C.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Review Manuscript

Leveraging Battery Performance through Mechanically Interlocked Polymers

Yangju Lin,^{a,b*} Mingrui Liang,^a and Ahmed Eldeeb^aReceived 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

1. Introduction

Innovation in clean and renewable energy technologies is essential to address the global impact of climate change and the impending depletion of fossil fuel resources. Batteries play a critical role in these technologies due to their importance in energy storage and release. Primarily composed of anode and cathode materials separated by electronically insulating yet ionically conductive electrolytes, batteries operate by transporting metal cations between electrodes through the electrolyte medium, driven by differences in redox potential. Concurrently, electrons flow through an external circuit, enabling energy storage during charging and controlled energy release during discharging.¹ By developing specialized high-tech components that often include novel polymeric materials,^{2,3} batteries can be optimized for specific performance metrics such as high-energy density, long cycling life and high battery safety—all particularly relevant for electric vehicle and portable devices. Such polymeric components, including polymer electrolytes, electrode binders and coatings (Figure 1a), are emerging as crucial elements of high-performance batteries. Innovation in this area remains an ongoing challenge in both basic and applied research. For example, polymer coatings have been developed to improve the cycling stability of high-energy density lithium (Li)-metal anodes by providing robust protection, improved interfacial contact, and prevention of dendrite formation;^{4,5} polymer electrolytes have been widely applied to improve battery stability and safety by overcoming the leakage and flammability issues related to liquid electrolytes;^{6,7}

and polymer binders are employed to dramatically improve electrode cycling stability by supporting mechanical integrity and enhancing capacity retention during repeated charge/discharge cycles.^{8–11}

Polymer materials containing mechanical bonds,¹² also known as mechanically interlocked polymers (MIPs),¹³ represent an emerging category of polymer materials. Their key components—mechanical bonds—feature both high spatial freedom (i.e., rotation and

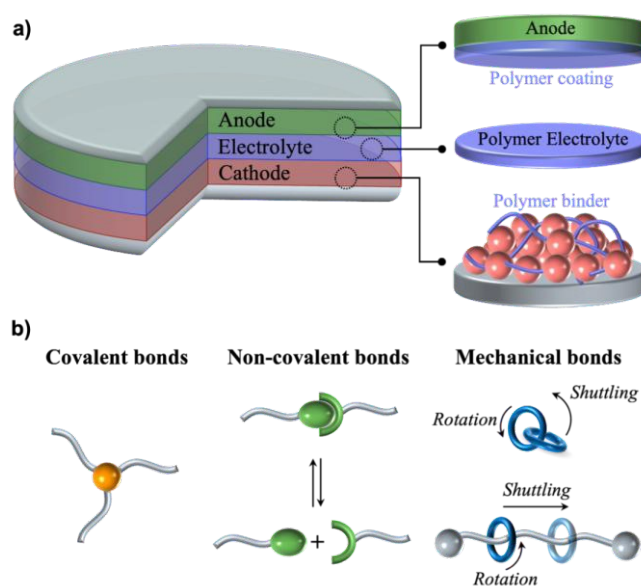


Figure 1 a) Typical “sandwich” structure of batteries, with potential polymeric components indicated. b) Schematic of conventional covalent bonds, non-covalent bonds and mechanical bonds (such as catenanes and rotaxanes) in polymer materials.

^aDepartment of Chemistry, ^bWaterloo Institute for Nanotechnology, University of Waterloo, Waterloo, Ontario N2L 3G1, Canada.

E-mail: yangju.lin@uwaterloo.ca



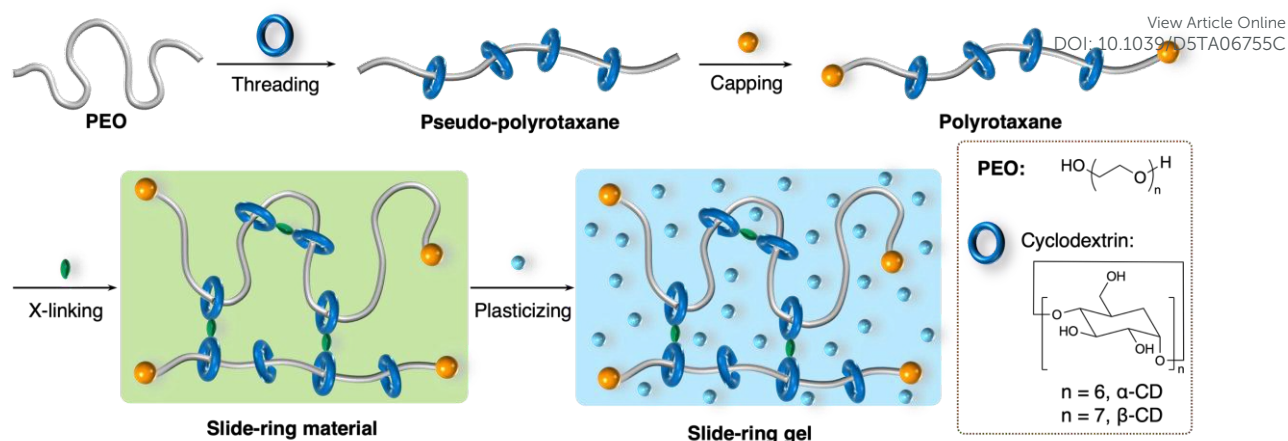


Figure 2 Representative scheme of preparation of mechanically interlocked polymer electrolytes using PEO and CDs. The materials generated in each step—pseudo-polyrotaxane (pseudo-PR), polyrotaxane (PR), slide-ring material (SRM) and slide-ring gel (SRG)—can be adapted to polymer electrolytes by introducing various salts.

shuttling) and mechanical strength comparable to covalent bonds (Figure 1b),^{14–16} endowing MIPs with combined mechanical robustness and adaptability.¹⁷ Existing MIP designs include slide-ring materials developed by Ito et al.,¹⁸ networks via in situ threading and crosslinking by Harada and Takashima et al.,¹⁹ rotaxane crosslinked networks by Takata et al.,²⁰ and mechanical interlocked networks with dense mechanical bonds by Yan et al.,¹² and threaded polycatenanes and polycatenane networks by Rowan and coworkers,²¹ to name a few. Many of these MIPs have recently demonstrated efficacy in enhancing battery performance, broadly attributed to their unique adaptability and mechanical resilience derived from the mechanical bonds. However, the detailed molecular mechanisms that lead to the enhanced device-level performance have yet to be fully understood.

While the development of novel MIPs remains an area of great interest, their potential applications—including use as electrolytes,^{22–24} electrode coatings,^{25,26} binder materials,²⁷ and in stretchable electronics,^{28,29}—have only recently begun to be explored. A foundational challenge to advancing these technologies is the particularly arduous synthesis of MIPs, which stems from the complex design of sophisticated mechanical bond motifs. This complexity is particularly problematic when scaling production for device fabrication. For example, cyclic molecules used as hosts for mechanical bond construction often require multi-step synthesis and are typically obtained in low yields.^{20,30} Nevertheless, recent efforts have demonstrated unprecedented potential for MIPs in battery applications. To this end, this minireview presents recent progress in leveraging MIPs as battery materials, aiming to inspire innovative and scalable MIP designs and highlight significant opportunities at the MIP-battery research interface.

In this review, the use of MIPs in batteries is categorized as polymer electrolytes, electrode binders, and electrode coatings. While most studies focus on polymer electrolytes, fewer studies address electrode binders and coatings. Section 2 reviews MIP applications as both solid-state and gel polymer electrolytes, with Section 2.1 highlighting how polymer structural designs influence ion-transport behaviour. Integration of these electrolytes into full batteries is discussed separately in Section 2.2 and 2.3. Section 3 covers MIP binders specifically for silicon (Si) anodes, with no

reported applications for other electrode materials to date. Section 4 introduces recent examples of MIPs as protective coatings, or artificial solid electrolyte interphases (SEIs), for high-energy-density Li-metal anodes. Finally, Section 5 discusses challenges and opportunities in leveraging MIPs as battery materials.

2. MIPs as Polymer Electrolytes

In contrast to conventional liquid electrolytes, which are infiltrated into polyolefin-based porous membranes to serve as ion-conducting media, polymer electrolytes function as both electrode insulators and ion conductors. Consequently, they must possess sufficient mechanical strength and ion conductivity. While tuning and enhancing polymer mechanical strength is well established in polymer science, achieving sufficient high ionic conductivity—especially in the solid state ($> 10^{-4} \text{ S} \cdot \text{cm}^{-1}$)—has remained a persistent challenge since their inception.³¹ Nevertheless, polymer electrolytes (both solid-state and gel types) offer potential solutions to safety concerns associated with liquid electrolyte systems, such as leakage and flammability. MIPs exhibit superior mechanical strength, resilience, and unique polymer dynamic behavior owing to the molecular freedom and dynamics related to mechanical bonds. Crucially, their polymer dynamics (e.g., segmental motion and diffusion) may be strongly linked to ion conduction, which pose compelling scientific questions for further exploration.

2.1 MIP polymer electrolytes

2.1.1 MIP solid-state electrolytes. Ion conduction in solvent-free solid-state polymer electrolytes can be largely dictated by the salt solvation condition and polymer segmental motion.^{31,32} Generally, polymers with high segmental motion (or a low glass transition temperature, T_g) are beneficial for ion conduction.^{33–37} Conversely, salt with high dissociation ability and bulky anions typically enhance ion conduction by increasing the concentration of solvated ions. Moreover, an optimal content of salt is necessary to maximize the charge carriers while avoiding excessive complexation with polymer



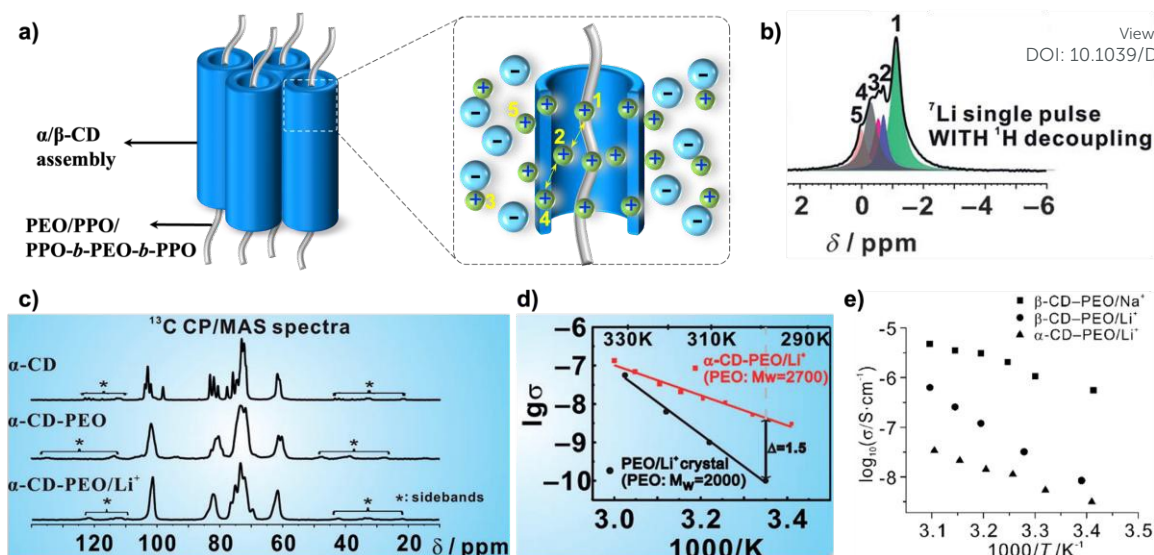


Figure 3 a) Pseudo-PR electrolytes consisting of nanochannels that enhance ion transport. b) Solid-state ^7Li NMR revealing five types of Li^+ species within the pseudo-PR electrolytes. c) ^{13}C CP/MAS spectra comparison of $\alpha\text{-CD}$, $\alpha\text{-CD-PEO}$ and $\alpha\text{-CD-PEO/Li}^+$, indicating the formation of nanochannels within the pseudo-PR electrolyte. d) Temperature-dependent ionic conductivity of pseudo-PR electrolyte and conventional PEO/Li electrolyte, demonstrating enhanced ion transport and distinct transportation mechanisms. e) Effect of host size and ion species on the ionic conductivity of pseudo-PR electrolytes containing nanochannels, where large host size enhances chain segmental motion and presumably lower charge density in ion species facilitates the ion transport within the nanochannels. b), c) and d) are reproduced from reference [45] with permission from Wiley, copyright 2014; e) is reproduced from reference [46] with permission from Wiley, copyright 2015.

chains, which can restrict chain segmental motion and hinder ion conductivity.^{38–40} To date, poly(ethylene oxide) (PEO)-based solid-state electrolytes remain the most ion-conductive among polymer electrolytes when formulated with an optimal salt content that effectively suppresses matrix crystallinity without excessive physical crosslinking due to dative interactions.^{41–43} Similarly, enhanced segmental mobility has been found critical for improving ion conduction in solid-state PEO electrolytes. Recent computational studies indicate that abundant solvation sites and continuous ion-conducting paths within solid-state PEO electrolytes are responsible for their relatively high ionic conductivity.⁴⁴

Cyclodextrin (CD)-PEO-based polyrotaxanes (PRs) have been the most studied MIPs for solid-state electrolytes (Figure 2). The use of O-rich PEO chains as the axles and hydroxyl group-abundant CDs as the wheels makes these MIPs desirable as solid media for salt dissolution. Building on earlier studies of PRs, Chen and Yao et al.⁴⁵ first reported a crystalline pseudo-PR electrolyte consisting of $\alpha\text{-CD}$ threaded PEO ($\alpha\text{-CD-PEO}$) and LiAsF_6 salt (electrolyte denoted as polymer/ion, $\alpha\text{-CD-PEO/Li}^+$) in 2014 (Figure 3a). A short PEO chain ($M_w = 2700$ Da) was mixed with LiAsF_6 salt at a controlled ethyl oxide (EO) repeating unit to Li^+ ion ratio (EO: Li^+), then added to a saturated aqueous $\alpha\text{-CD}$ solution to spontaneously generate crystalline pseudo-PR electrolytes. Although the specific average number of $\alpha\text{-CD}$ threaded onto each PEO chain was not characterized, the obtained crystalline electrolyte was found to form ordered nanochannels as revealed by ^{13}C cross-polarization/magic angle spinning (CP/MAS) NMR spectroscopy (Figure 3a). When the EO: Li^+ equals 2, these nanochannels provide a directional pathway and result in an ionic conductivity of $\sim 5.6 \times 10^{-9} \text{ S cm}^{-1}$ at 29°C —1.5 orders of magnitude higher than a control electrolyte comprising PEO ($M_w = 2000$ Da) and LiSbF_6 salt. Temperature-dependent conductivity analysis indicated a lower activation energy of $E_a = 75.1 \text{ kJ mol}^{-1}$ compared to the control electrolyte ($E_a = 160.4 \text{ kJ mol}^{-1}$) (Figure 3d).

Detailed solid-state ^7Li spectra revealed five types of Li^+ species in the crystalline electrolyte, with types 1, 2 and 4 Li^+ located within the nanochannels while excluding the larger AsF_6^- anion. Notably, type 2 Li^+ acts as a transmitter, exchanging with type 1 and 4 Li^+ ions and facilitating ion transfer within the nanochannels (Figure 3a and 3b). This Li^+ exchange, which is coupled to PEO chain motion within the nanochannels, enabled efficient ion conduction with an activation energy of $E_a = 42.1 \text{ kJ mol}^{-1}$. The observed relatively low macroscopic ionic conductivity ($\sim 2.6 \times 10^{-7} \text{ S cm}^{-1}$ at 29°C) was further attributed to grain boundary resistance.

To improve the PEO chain segmental motion within the nanochannels and thereby enhance ion conductivity, Chen and Yao et al.⁴⁶ applied $\beta\text{-CD}$ as the host molecule to leverage its larger cavity size compared to $\alpha\text{-CD}$ ($6.0 \text{ \AA}$ vs. $4.7 \text{ \AA}$). The resulting $\beta\text{-CD-PEO/Li}^+$ electrolyte ($\beta\text{-CD:EO:Li}^+ = 1.2:6:1$) formed similar nanochannels and showed slightly higher ionic conductivity than the $\alpha\text{-CD-PEO/Li}^+$ electrolyte (Figure 3e). However, the activation energy for ion conduction in $\beta\text{-CD-PEO/Li}^+$ was found to be higher than that of $\alpha\text{-CD-PEO/Li}^+$ ($123.2 \text{ kJ mol}^{-1}$ vs. 75.1 kJ mol^{-1}). They further prepared a $\beta\text{-CD-PEO/Na}^+$ electrolyte to demonstrate the applicability of these nanochannel structures. Using ^2H NMR with deuterated PEO as the axle, both $\beta\text{-CD-PEO/Li}^+$ and $\beta\text{-CD-PEO/Na}^+$ showed improved PEO chain segmental mobility compared to $\alpha\text{-CD-PEO/Li}^+$. Notably, the higher ionic conductivity observed in $\beta\text{-CD-PEO/Na}^+$ relative to $\beta\text{-CD-PEO/Li}^+$ could be attributed to the lower charge density of Na^+ compared to Li^+ , which reduces binding strength to O atoms and facilitates ion transport. In a subsequent study,⁴⁷ they examined the effect of chain mobility on ionic conductivity using poly(propylene oxide) (PPO, $M_w = 2000$ Da) polymer and PPO-PEO-PPO



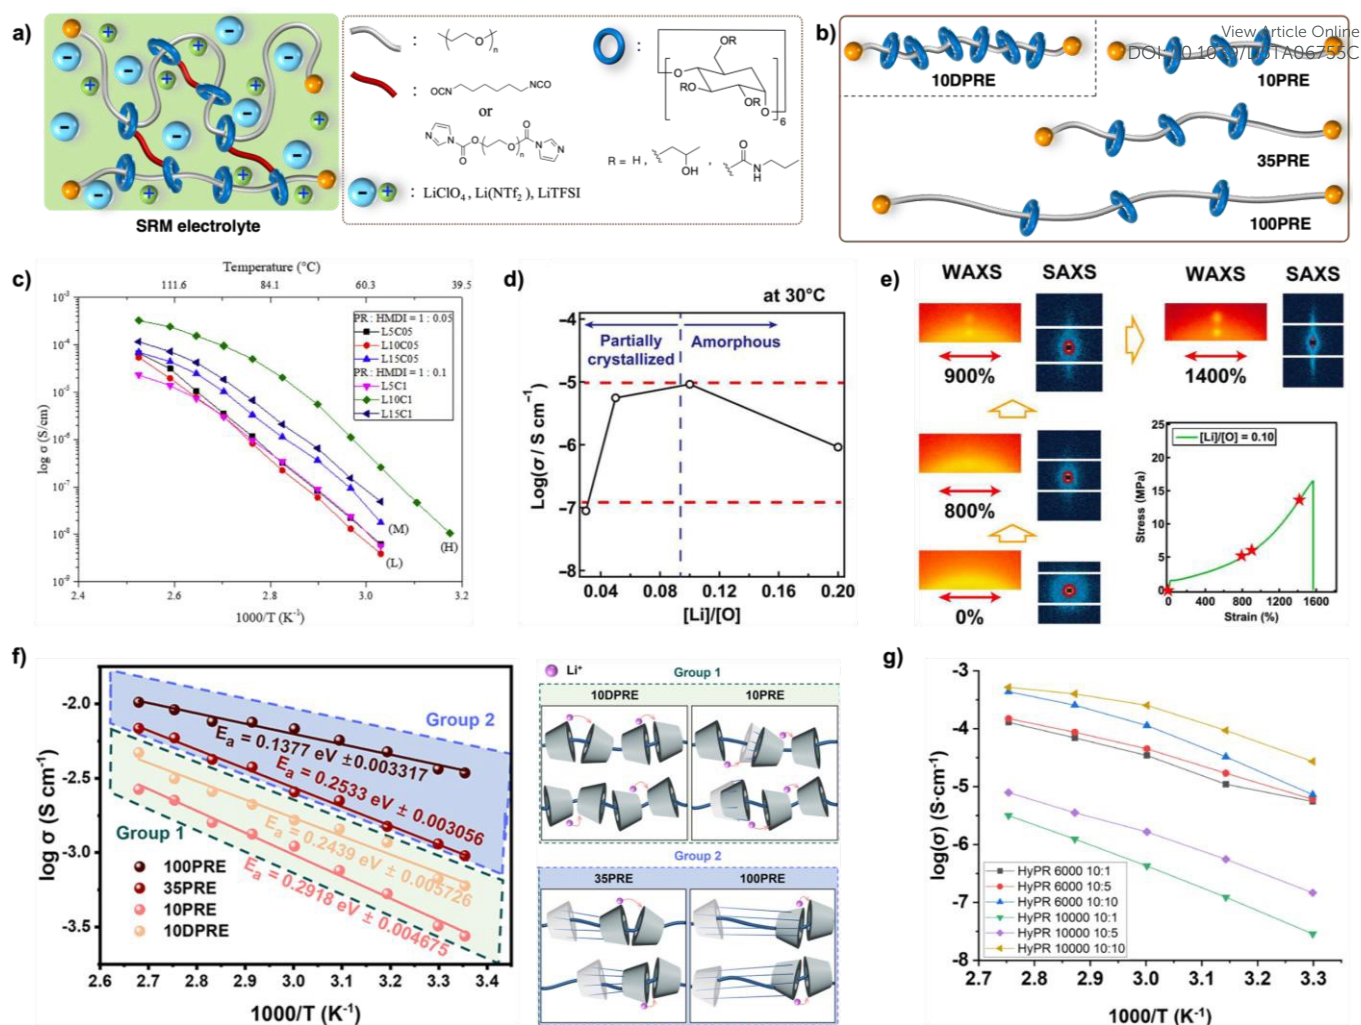


Figure 4 a) Compositions of SRM electrolytes in reported literature, with various crosslinkers, salts and modified CDs. b) Tunable PRs with varied axle lengths (10, 35 or 100 kDa) and wheel density (20 or 35 CDs per chian) for the fabrication of SRM electrolytes. c) Temperature-dependent ionic conductivity of SRM electrolyte with various salt contents and crosslinking densities. LxCy: x = 5, 10, 15 wt% Li(NTf₂) salt; y = 05 or 1 for 5 and 10 mol% hexamethylene diisocyanate crosslinker, respectively. d) Evolution of ionic conductivity over Li⁺/EO (or [Li]/[O]) ratio in the SRM electrolytes. e) WAX and SAXS studies of crystallinity in SRM electrolyte under different strains. f) Impact of PEO chain length and CD density in PR on the ionic conductivity of fabricated SRM electrolytes. g) Effects of the chain length of macrolinker and crosslinking density on the ionic conductivity of SRM electrolytes. For the legends, HyPR6000/10000 refers to the use of hydroxypropyl modified CDs and 6/10 kDa macrolinker, and the following ratio indicates the PR and macrocrosslinker weight ratios. c) is reproduced from reference [23] with permission from Elsevier, copyright 2018; d) and e) are reproduced from reference [49] with permission from Science Advanced, copyright 2024; f) reproduced from reference [50] with permission from American Chemical Society, copyright 2024; and g) reproduced from reference [51] with permission from American Chemical Society, copyright 2024.

blockcopolymer (CoP, EO:PO = 1.38:1, M_w = 2000 Da) as the axels. Both produced crystalline electrolytes with nanochannel structures. Strikingly, the ionic conductivity of β -CD-CoP/Li⁺ (β -CD:[PO+EO]:Li⁺ = 1:2.3:1.23) was four orders of magnitude higher than that of β -CD-PPO/Li⁺ (β -CD:PO:Li⁺ = 1:2.4:1.53) at 25 °C (3.2×10^{-5} S cm⁻¹ vs. 9.5×10^{-9} S cm⁻¹). Solid-state ¹H MAS NMR confirmed that β -CD-CoP/Li⁺ has a higher segmental mobility than β -CD-PPO/Li⁺. It should be noted that the MIP electrolytes investigated by Chen and Yao et al. are, in fact, linear pseudo-PRs, as no chain-end capping step was performed and the threading of CDs onto the short axle polymers was relatively uncontrolled.

The mechanically trapped CDs on α -CD-PEO PRs can be crosslinked to produce crosslinked PRs, also known as slide-ring materials (SRMs) (Figure 2), a concept first demonstrated and extensively explored by Ito and coworkers since 2001.⁴⁸ In 2017, Yokoyama and Ito et al.²³ fabricated a series of solid-state SRM

electrolytes based on α -CD-PEO PRs. In the study, an α -CD-PEO PR consisting of a M_w = 35000 PEO and ~ 100 threaded α -CDs was mixed with varying LiClO₄ contents and further crosslinked using hexamethylene diisocyanate (HDI) (Figure 4a). Although the exact number of crosslinking sites per chain was not provided, doubling the crosslinking sites was insufficient to suppress crystallinity. Instead, increasing the LiClO₄ content from 5wt% to 15wt% successfully eliminated crystalline domains (Figure 4c). However, the achieved ionic conductivity remained relatively low (10^{-9} – 10^{-7} S cm⁻¹) at ~ 80 °C. Notably, the temperature-dependent ionic conductivity exhibited a segmental motion-dictated trend at high temperatures, while showing Arrhenius-type behaviour at low temperatures—a phenomenon attributed to hydrogen-bonded CDs that limit segmental mobility. To address this limitation, they further reduced the hydrogen bonding level by reacting the hydroxyl groups on CDs using propyl isocyanate. Consequently, increasing the degree of hydroxyl substitution on CD to 22% improved the ionic conductivity



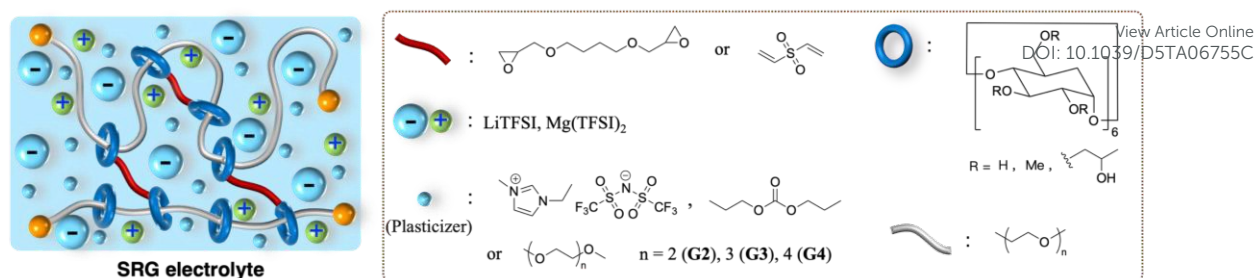


Figure 5 Schematic compositions of SRG electrolytes in reported literature, including various crosslinkers, salts, modified CDs and plasticizers.

(although still relatively low at $\sim 10^{-7}$ S·cm⁻¹) and enhanced mechanical ductility. Further increasing the substitution to 49% adversely reduced the ionic conductivity and ductility owing to hydrophobic aggregation of modified CDs. Later, Ito, Mayumi and Hashimoto et al.⁴⁹ sought to improve the Young's modulus of SRM electrolytes through fine-tuning PEO crystallinity and CD aggregation. An α -CD-PEO PR, composed of PEO ($M_w = 35000$ Da) and 9 α -CDs per PEO chain, was blended with varying Li(NTf₂) salt contents (EO:Li⁺ = 5–33) and then crosslinked using HDI. Increasing the EO:Li⁺ ratio (i.e., decreasing Li(NTf₂) salt content) led to higher PEO crystallinity and Young's modulus without compromising maximum strain (Figure 4d). All prepared SRM electrolytes were stretchable and exhibited strain-induced crystallization, which further enhances the electrolytes' mechanical strength (Figure 4e). Importantly, the ionic conductivity first increased and then decreased, with a maximum value of $\sim 10^{-5}$ S·cm⁻¹ achieved at EO:Li⁺ = 10. This work demonstrated a breakthrough in overcoming the commonly known trade-offs among electrolyte modulus, ductility, and ionic conductivity.

In 2024, Seo and coworkers comprehensively investigated a series of SRM electrolytes composed of α -CD-PEO PRs with systematically varied lengths of PEO chains ($M_w = 10,000$, 35,000, and 100,000 Da) and different numbers of threaded α -CDs per chain (35 or ~ 20) (Figure 4b).⁵⁰ Overall, a higher number of α -CDs per chain led to increased formation of crystalline α -CD structures, thereby reducing α -CD mobility along the chain. These PRs were blended with LiNO_3 salt and further crosslinked to produce four SRM electrolytes. Comparing PRs with ~ 20 threaded α -CDs but different PEO chain lengths (10PRE, 35PRE and 100PRE in Figure 4b and 4f), longer PEO chains provided greater α -CD sliding mobility, correlating with higher ionic conductivity. In this system, Li^+ ionic conduction appears coupled to α -CD sliding mobility. However, for the shortest PEO chain ($M_w = 10,000$ Da), increasing the number of threaded α -CDs from ~ 20 to 35 (10PRE vs. 10DPRE) increased the ionic conductivity despite decreased α -CD sliding mobility. ^7Li NMR studies attributed this effect to enhanced LiNO_3 dissociation related to higher α -CD content. As such, Li^+ conduction in PRs with high α -CD content was postulated to occur through hopping along the threaded and aligned α -CDs. The SRM electrolytes design demonstrated significant advantages over controls comprising PEO and physically blended α -CDs, with ionic conductivity enhanced by a factor of ~ 330 . Notably, an impressive ionic conductivity of $3.4 \times 10^{-3} \text{ S}\cdot\text{cm}^{-1}$ at 25°C was reported using the PEO with $M_w = 100,000$ Da and ~ 20 threaded α -CDs.

Yin and You et al.⁵¹ also reported SRM electrolytes employing α -CD-PEO PRs combined with PEO macromolecular crosslinkers instead

of small-molecule crosslinkers. A PEO with $M_w = 35,000$ Da was used to prepare a PR containing ~ 100 threaded α -CDs, with the α -CDs were further functionalized with hydroxypropyl groups before crosslinking with modified PEO macrolinkers ($M_w = 6,000$ or $10,000$ Da). At 15 wt% LiTFSI content, the as-prepared SRM electrolytes showed substantially reduced α -CD crystallinity and slightly increased PEO crystallinity with increasing amounts of PEO macrolinkers, offering improved electrolyte ductility. Similarly, longer PEO macrolinkers (10,000 vs. 6,000 Da) led to reduced α -CD crystallinity but slightly increased PEO crystallinity. Overall, increased macrolinker content or longer macrolinker length resulted in SRM electrolytes with higher polymer segmental mobility and corresponding enhanced ionic conductivity (Figure 4g). All prepared electrolytes showed good thermal stability > 150 °C. The α -CD crystalline domains, which govern chain segmental mobility and ionic conductivity, could be eliminated by heat treatment. As a result, all SRM electrolytes exhibited improved ionic conductivities, with a maximum conductivity of $2.7 \times 10^{-5} \text{ S}\cdot\text{cm}^{-1}$ at 30 °C. Pursuing further improvements, a longer PEO macrolinker with $M_w = 35,000$ was applied to fabricate SRM electrolyte.⁵² Despite an increase in PEO crystallinity, the α -CD crystallinity responsible for chain segmental mobility was successfully suppressed as the macrolinker length increased from $M_w = 6000$ Da to $M_w = 35,000$ Da. Overall, the SRM electrolyte with a PEO macrolinker of $M_w = 10,000$ Da provided the optimal ionic conductivity of $7.05 \times 10^{-5} \text{ S}\cdot\text{cm}^{-1}$ at 30 °C.

2.1.2 MIP gel electrolytes. The addition of plasticizers to a polymer electrolyte enhances chain segmental mobility and modifies ion conduction mechanisms, resulting in substantial improvements in ionic conductivity (Figure 5). Plasticizers act as “molecular lubricants”, disrupting interchain interactions such as hydrogen bonding and van der Waals forces, while simultaneously increasing the free volume within the polymer matrix. This combination remarkably enhances chain segmental mobility, facilitating ion transport. Meanwhile, plasticizers solvate the salt and enable ions to transport more readily along the liquid path within the polymer matrix, effectively lowering activation energy for ion transport.^{53–55} However, these benefits come with trade-offs including reduced mechanical strength and potential safety risks due to the flammability of added plasticizer. To worth mentioning, the polymer osmotic pressure allows the plasticizer to be retained within the polymer matrix, mitigating the leakage of liquid plasticizer.

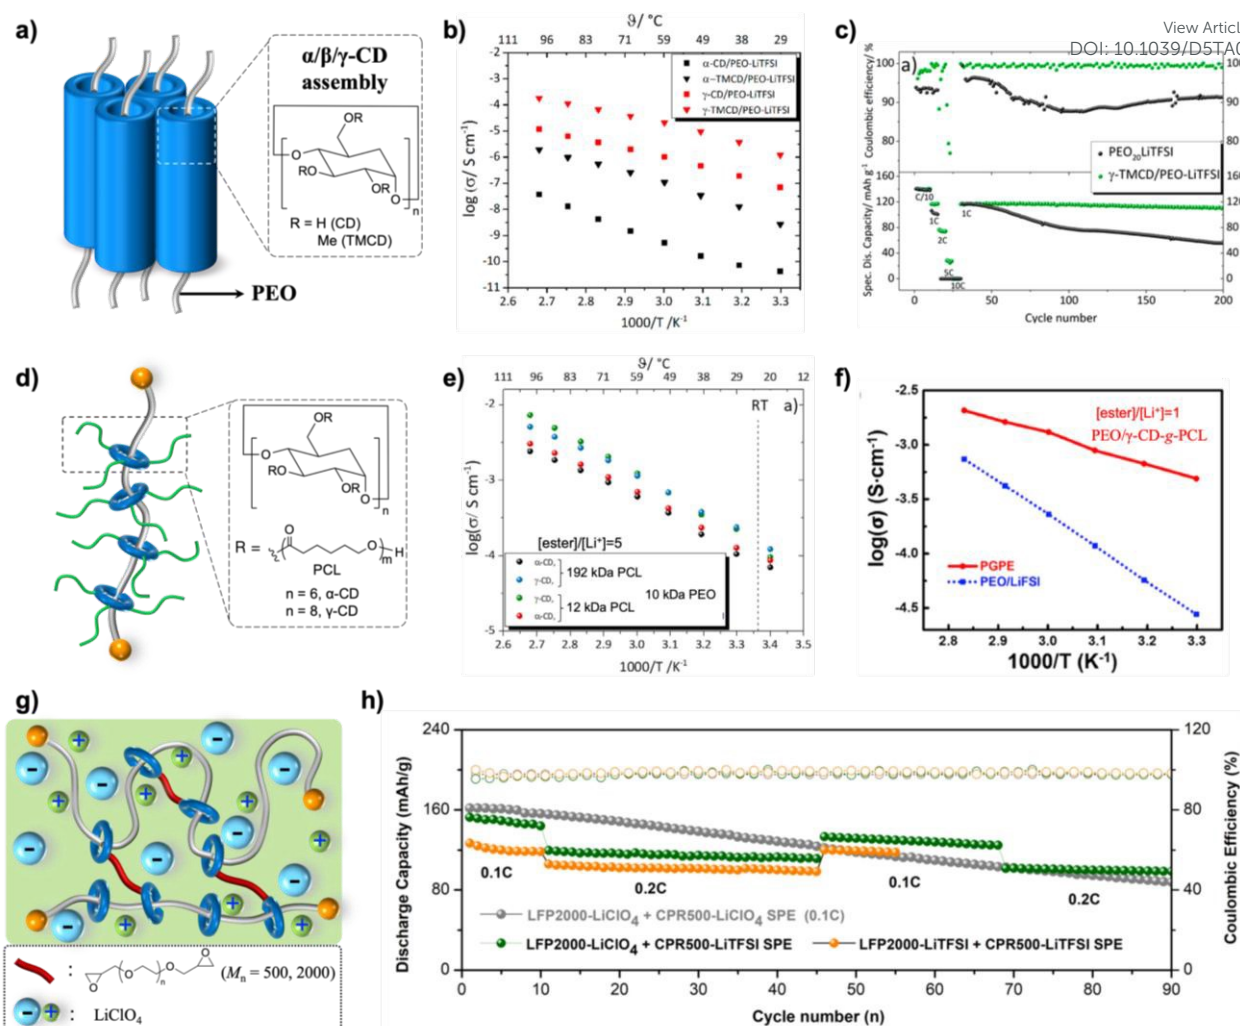


Figure 6 a) Pseudo-PR electrolytes consisting of different CDs and LiTFSI salt show nanochannel structures, and their corresponding temperature-dependent ionic conductivity properties are shown in b). c) The use of a pseudo-PR electrolyte comprising of methylated γ -CD and PEO presents improved cycling stability compared with a conventional PEO/LiTFSI electrolyte. d) Schematic PR electrolytes containing PCL-grafted CD wheels. e) The length effect of grafted PCL (12 or 192 kDa) and CD species (α - or γ -CD) on the PR electrolyte ionic conductivities. f) Ionic conductivity of a “polymer-in-salt” electrolyte containing PCL-grafted-CD/PEO PR (38 wt%) and LiFSI salt (62 wt%). g) SRM electrolyte with macrolinker and its performance in an LFP||Li full battery (CPR500 refers to SRM electrolyte crosslinked using a 500 Da PEO macrolinker). b) and c) are reproduced from reference [59] with permission from American Chemical Society, copyright 2018, e) is reproduced from reference [24] with permission from Elsevier, copyright 2019, f) is reproduced from reference [62] with permission from American Chemical Society, copyright 2019, and h) is reproduced from reference [62] with permission from Elsevier, copyright 2024.

Slide-ring gels (SRGs) developed by Okumura and Ito⁴⁸ exhibited excellent mechanical ductility owing to the adaptive shuttling of α -CDs under external mechanical load. Consequently, SRGs offer a promising approach for the fabrication of gel electrolytes that address the trade-off between ionic conductivity and mechanical strength. Building on previous studies on SRGs, Shimomura and Ito et al.⁵⁶ investigated the conductivity and mechanical strength of α -CDs-PEO-based SRG electrolytes swollen with propylene carbonate and LiTFSI salt. A PR composed of a PEO with $M_w = 35,000$ Da and ~ 100 threaded α -CDs was crosslinked with various amounts of divinyl sulfone crosslinker. Due to poor affinity of propylene carbonate toward α -CDs, the SRM could not be swollen to form SRG electrolyte. However, after 28% or 74% methylation of α -CDs' hydroxyl groups, SRMs could be successfully swollen (swelling ratios of 107–108%) to give SRG electrolytes exhibiting high ionic conductivity of $2.2\text{--}3.9 \times 10^{-3} \text{ S cm}^{-1}$ at 25 °C. Slightly reducing crosslinking density moderately improved ionic conductivity while slightly reducing modulus. Notably, the activation energy for ion conduction was comparable to

that of a pure electrolyte solution, suggesting a similar ion conduction mechanism to liquid electrolyte. Alternatively, Shimomura and Ito et al.⁵⁷ utilized a series of imidazolium-based ionic liquids to prepare the SRG electrolyte. α -CDs with and without 50% hydroxypropyl substitution were applied to fabricate the SRG electrolytes, which swelled slowly in the ionic liquids over a week. Obtained SRG electrolytes showed Young's moduli of 15–30 kPa and high ionic conductivities of $1.66\text{--}3.18 \times 10^{-3} \text{ S cm}^{-1}$ at 20 °C, with 1-ethyl-3-methylimidazolium ethyl sulfate providing the highest ionic conductivity. Further addition of LiTFSI salt to the ionic liquid improved the ionic conductivity ($2.66\text{--}4.31 \times 10^{-3} \text{ S cm}^{-1}$ at 30 °C) and mechanical properties (8.4–60.5 kPa Young's modulus), rendering the SRG electrolytes suitable for Li-ion batteries.²²

Shimomura and Ito et al.⁵⁸ further expanded this SRG system to gel electrolytes containing Mg^{2+} ion, using $0.5 \text{ mol L}^{-1} \text{ Mg(TFSI)}_2$ in diethylene glycol dimethyl ether (diglyme; G2), triethylene glycol dimethyl ether (triglyme; G3), or tetraethylene glycol dimethyl ether



(tetraglyme; G4) as swelling liquid electrolytes. Interestingly, swelling behaviour was highly dependent on the glyme solvent: G4 showed no swelling, while G2 and G3 reached swelling equilibrium in one and three weeks, respectively. It was postulated that exclusive coordination of Mg^{2+} with G4 prevents its interaction with α -CD and PEO chains, inhibiting the network swelling property. G3 provided the highest swelling ratio and the greatest electrolyte uptake and was therefore systematically evaluated by varying crosslinking density. Increasing crosslinking density improved modulus but reduced ductility and ionic conductivity. The ion conduction was found to follow a segmental motion-coupled ion transportation mechanism, with an optimized ionic conductivity of $1.73 \times 10^{-3} \text{ S cm}^{-1}$ at 25°C .

2.2 MIP solid-state electrolytes for batteries

Like other solid-state polymer electrolytes, the relatively low ionic conductivity in MIP solid-state electrolytes remains a long-standing challenge for their application in full batteries. Initial attempts have successfully demonstrated their application potential at elevated temperatures. In 2018, Brunklaus, Winter and colleagues prepared a series of pseudo-PR electrolytes using a short chain PEO ($M_w = 2000$) and both pristine and methylated α -, β -, γ -CDs (Figure 6a).⁵⁹ The prepared electrolytes had a CD:EO ratio of 1:2.8 and exhibited nanochannel structures similar to those reported by Chen and Yao et al.^{45–47} after being blended with LiTFSI salt at an EO:Li ratio of 5:1. Interestingly, all methylated CDs exhibited higher ionic conductivity than the pristine counterparts, attributed to their less rigid structures due to the absence of hydrogen bonds between CDs. Notably, the ionic conductivity followed the trend α -CDs < β -CDs < γ -CD, correlating with cavity size-dependent PEO chain segmental mobility (Figure 6b). Consequently, the methylated γ -CD electrolyte showed an ionic conductivity of $\sim 10^{-4} \text{ S cm}^{-1}$ at 100°C , with a transport number of $t_+ \sim 0.34$. This electrolyte was further demonstrated to outperform a control PEO/LiTFSI electrolyte in full battery tests (Figure 6c). Brunklaus and Winter et al.²⁴ further investigated CD-PEO based PR electrolytes containing polycaprolactone (PCL) grafted CDs (Figure 6d), following a preparation method previously reported by Kato et al.⁶⁰ A similar low molecular weight PEO ($M_w = 3000$) was used to prepare chain-end capped PR. Although the CD coverage ratio was unspecified, the number of grafted caprolactone units per CD was varied from 48 to 103. The use of γ -CD grafted long PCL chains and at a LiTFSI salt content of [ester]:[Li⁺] = 5:1 provided optimal ionic conductivity, with impressive values $> 10^{-4} \text{ S cm}^{-1}$ at room temperature and $10^{-3} \text{ S cm}^{-1}$ at 60°C (Figure 6e). A Li||Li symmetric cell employing this PR electrolyte exhibited stable cycling for > 600 cycles under a current of 0.1 mA cm^{-2} at both 40°C and 60°C .

The concept of polymer-in-salt,⁶¹ in which salt is the major component (> 50 wt%), has been shown to yield relatively high ionic conductivity in solid-state electrolytes. A similar PCL-grafted γ -CD-PEO PR (38wt%) and LiFSI (62wt%) were mixed and infiltrated into a porous polyimide film to prepare the PR-in-salt electrolyte.⁶² The obtained electrolyte exhibited a high ionic conductivity of $4.89 \times 10^{-4} \text{ S cm}^{-1}$ at 30°C (Figure 6f) and demonstrated superior cycling in Li||Li symmetric cells and NCM811||Li full cells compared to a PEO/LiFSI counterpart. The improved battery performance was further revealed by transmission electron microscope (TEM) and X-ray photoelectron spectroscopy (XPS) studies of the NMC811 cathode

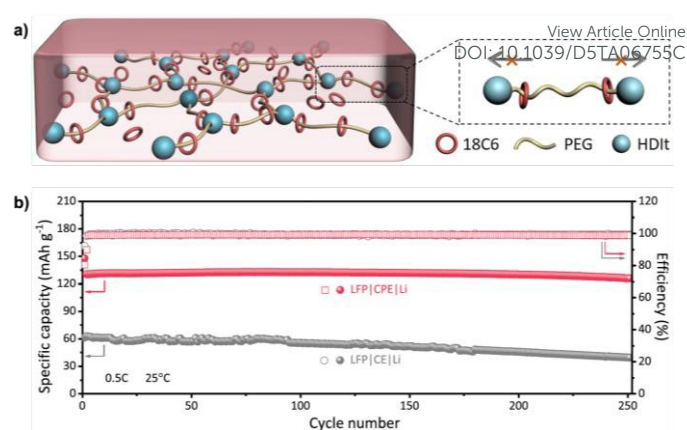


Figure 7 a) Schematic of a chain-end crosslinked PR network electrolyte (CPE) containing interlocked crown ethers, and b) its use in a LFP||Li full battery showing a stable and improved cycling at 25°C , compared with a non-interlocked counter part CE. Reproduced from reference [64] with permission from American Chemical Society, copyright 2023.

after cycling, which showed that a smooth uniform, continuous, and dense CEI layer resulting from the PR-in-salt electrolyte prevented transition metal dissolution and additional side reactions.

In another study, Gohy and Jia et al.⁶³ prepared several SRM electrolytes composed of α -CD-PEO PR (PEO $M_w = 35000$ Da with ~ 100 threaded α -CDs), PEO crosslinker, and LiClO₄ salt (Figure 6g). By tuning the PEO crosslinker length ($M_w = 500$ or 2000 Da) and LiClO₄ salt content (EO:Li = 8:1–20:1), an optimal ionic conductivity of $7.25 \times 10^{-4} \text{ S cm}^{-1}$ at 60°C was achieved using a PEO crosslinker with $M_w = 500$ and EO:Li⁺ = 10:1. Consequently, this optimized SRM electrolyte was demonstrated in both Li||Li symmetric cells and LFP||Li full cells to provide stable cycling at 60°C (Figure 6h). Notably, the LFP cathode was fabricated using 40wt% SRM electrolyte as the binder or catholyte.

Beyond CD-PEO based PR electrolytes, Yu, Guo, and Tang et al.⁶⁴ designed a chain-end crosslinked PR electrolyte containing threaded 18-crown-6-ether rings on the PEO network strands (Figure 7a). This novel MIP electrolyte was prepared through in-situ threading and crosslinking of PEO chains in the presence of 18-crown-6-ether rings. Although the number of threaded crown ether rings was not specified, the obtained electrolyte exhibited an impressive ionic conductivity of $3.48 \times 10^{-4} \text{ S cm}^{-1}$ at room temperature. This electrolyte was further used to demonstrate stable cycling of a Li||Li symmetric cell and an LFP||Li full cell at 25°C (Figure 7b).

2.3 MIP gel electrolytes for batteries

The enhanced ionic conductivity in MIP gel electrolytes enables their practical application in batteries, albeit at the cost of compromised mechanical strength and thermal stability. Introducing external particles into the gel electrolyte to form a polymer composite gel electrolyte, enhances mechanical strength and thermal stability of gel electrolytes. Notably, the electronic states and physicochemical properties—including redox stability, dielectric constant, polymer crystallinity and relaxation dynamics, ionic conductivity, and surface energy—are indeed simultaneously modified when forming polymer composites. This collective alteration substantially influences the overall electrochemical performance.^{65,66} A similar strategy has also been explored in the context of MIP gel electrolytes. Tong et al.⁶⁷



performed a one-pot preparation of a pseudo-PR composite consisting of PEO ($M_w = 20,000$), α -CD (~ 32 α -CDs per PEO chain), poly(vinylidene fluoride-co-hexafluoropropylene) (PVDF-HFP), and liquid PEO ($M_w = 400$) (Figure 8a). This composite was subsequently immersed in an electrolyte solution containing $1 \text{ mol} \cdot \text{L}^{-1}$ LiPF_6 and an equal volume mixture of ethylene carbonate (EC), ethyl methyl carbonate (EMC), and dimethyl carbonate (DEC) (volume ratio of 1:1:1). Although the precise plasticizer fraction was not characterized, the composite gel electrolyte with a PEO:PVDF-HFP weight ratio of 1:2 provided an ionic conductivity of $1.73 \times 10^{-4} \text{ S} \cdot \text{cm}^{-1}$ at room temperature. This composite exhibited high thermal stability with $< 20\%$ shrinkage at 200°C , significantly outperforming a commercial Celgard 2400 membrane (Figure 8b). Cycling in a Li||Li symmetric cell and an LFP||Li full cell demonstrated promising stability (Figure 8c). Zhu and Tong et al.⁶⁸ further incorporated nano- Al_2O_3 particles to the gel electrolyte to reinforce both ionic conductivity and mechanical strength. The modified composite electrolyte exhibited an improved ionic conductivity of $8.30 \times 10^{-4} \text{ S} \cdot \text{cm}^{-1}$, a Li^+ transfer number of 0.51, and a tensile strength of 17.12 MPa. This enhancement is attributed to multiple molecular interactions including PEO-Li^+ , $\text{Al}_2\text{O}_3\text{-Li}^+$ and F-Li^+ were attributed to the enhancement. The new composite gel electrolyte exhibited improved cycling performance in an LFP||Li (LFP loading unspecified) full cell compared with the counterpart lacking nano- Al_2O_3 .

The pseudo-PR gel electrolyte was also applied in flexible Zinc-ion batteries, which possess high energy density, low cost, and intrinsic safety. Sun, Zhang and Miao et al.⁶⁹ prepared an α -CD-PEO pseudo-PR and subjected it to the in-situ polymerization of polyacrylamide (PAM) in the presence of $\text{Zn}(\text{OTf})_2$ salt, yielding a α -CD-PEO/PAM pseudo-PR hydrogel electrolyte containing both free α -

CDs and threaded α -CDs (Figure 8a). This hydrogel electrolyte exhibited higher mechanical toughness and adhesion compared to the PAM hydrogel electrolyte (Figure 8d). Impressively, a high room-temperature ionic conductivity of $22.4 \times 10^{-3} \text{ S} \cdot \text{cm}^{-1}$ with an outstanding Li^+ transfer number of 0.923 was achieved at 60 wt% water content, substantially outperforming the PAM electrolyte ($9.4 \times 10^{-3} \text{ S} \cdot \text{cm}^{-1}$) with the same water content. The use of this pseudo-PR hydrogel electrolyte in a $\text{La-V}_2\text{O}_5\|\text{Zn}$ ($\sim 1.0 \text{ mg} \cdot \text{cm}^{-2}$ $\text{La-V}_2\text{O}_5$ loading) coin cell demonstrated 90.2% capacity retention after 3500 cycles at $5 \text{ A} \cdot \text{g}^{-1}$ current density (Figure 8e). Additionally, the mechanical tough hydrogel electrolyte enabled flexible zinc-ion batteries resilient to various mechanical load such as bending, cutting, and puncturing.

Compared with (pseudo-)PR gel electrolytes, SRG electrolytes possess improved dimensional stability. Aiming to simultaneously improve the ionic conductivity and mechanical strength of gel electrolytes, Kim and Seo et al.⁷⁰ fabricated an SRG electrolyte based on α -CD-PEO PR (with PEO $M_w = 10,000$ Da) and a HDI crosslinker (Figure 9a). The glucose unit of α -CD was found to provide stronger solvation of LiNO_3 than LiTFSI and LiClO_4 , owing to strong binding between hydroxyl groups and NO_3^- anion (Figure 9b). Accordingly, a highly elastic SRG electrolyte containing LiNO_3 salt and 37 wt% DMSO exhibited a high ionic conductivity of $5.93 \times 10^{-3} \text{ S} \cdot \text{cm}^{-1}$ at 25°C , with a Li^+ transfer number of 0.71 and mechanical toughness of $14.3 \text{ MJ} \cdot \text{m}^{-3}$. The high ionic conductivity was attributed to the high free motion of threaded α -CDs, including sliding and rotation. The utilization of the SRG electrolyte was further demonstrated in an LFP||Li full cell at 25°C (Figure 9c). To enable the use of SRG electrolyte in Li-oxygen (O_2) batteries, Kim and Seo et al.⁷¹ later modified the threaded α -CD with acrylates and copolymerized the modified PR with butyl acrylate and PEO diacrylate to provide a

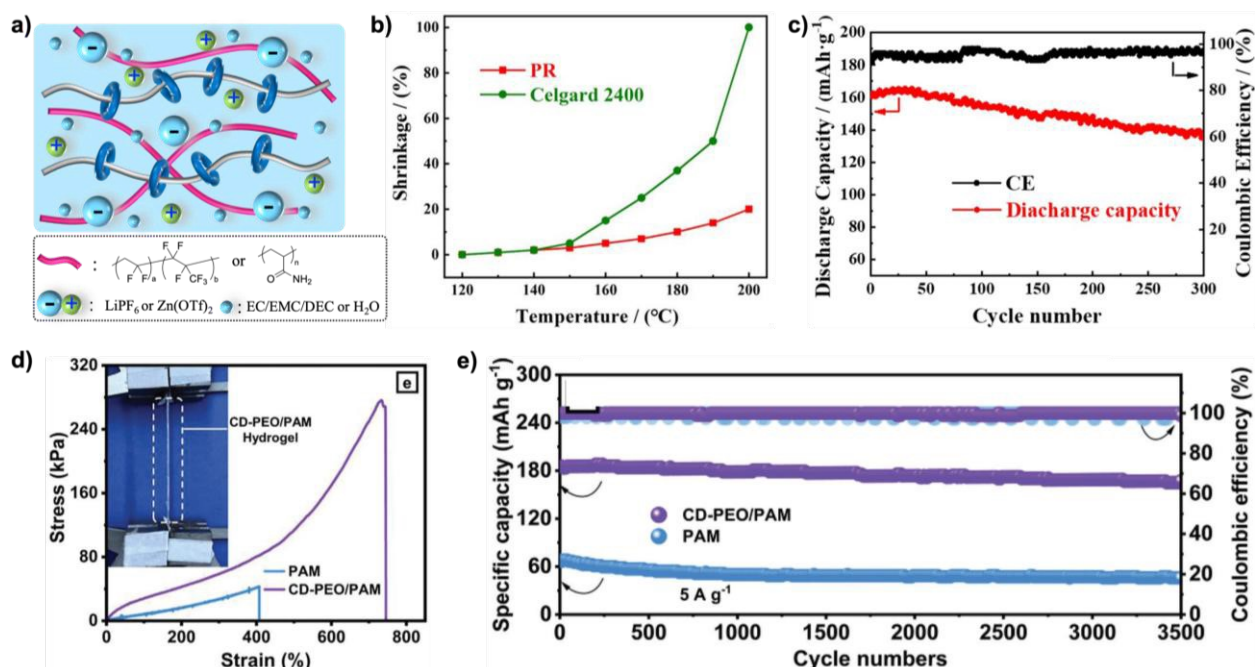


Figure 8 a) Composite gel electrolyte consisting of pseudo-PR and PVDF-HFP or PAM. b) Pseudo-PR composite gel electrolyte exhibits higher thermal stability than commercial Celgard 2400 membrane, and c) its use in a $\text{NMC532}\|\text{Li}$ battery enables 86% capacity retention after 300 cycles at 0.5C . A CD-PEO/PAM composite electrolyte showed higher d) mechanical toughness and e) cycling capacity in a $\text{La-V}_2\text{O}_5\|\text{Zn}$ battery than the PAM gel electrolyte. b) and c) are reproduced from reference [68] with permission from Springer, copyright 2022. d) and e) are reproduced from reference [69] with permission from Wiley, copyright 2023.



hydrophobic SRG electrolyte containing LiTFSI salt and 24% DMSO solvent (Figure 9d). The hydrophobic SRG electrolyte, exhibiting a high ionic conductivity of $2.8 \times 10^{-3} \text{ S cm}^{-1}$ and a Li^+ transfer number of 0.61 at 25 °C, offers high O_2 permeability while effectively repelling water molecules, as indicated by a reduced weight increase when exposed to humid air (Figure 9e). Both Li||Li symmetric cells and Li|| O_2 full cells exhibited excellent cycling stability (Figure 9f).

Gao and Ding et al.⁷² also reported an SRG electrolyte based on an α -CD-PEO PR (PEO with $M_n = 4000$ Da and 35 threaded α -CDs) crosslinked by PEO ($M_n = 2000$ Da) macrolinker. By optimizing the PR and PEO crosslinker composition, an SRG electrolyte containing 1 mol L^{-1} LiTFSI in a 1:1 (volume ratio) mixture of 1,2-dimethoxyethane (DME) and 1,3-dioxolane (DOL), with 1% LiNO_3 , achieved an ionic conductivity of 1.73×10^{-3} and a Li^+ transfer number of 0.71 at 30 °C. Consequently, an assembled LFP||Li coin cell showed long and stable cycling at 0.5–16C rate. Additionally, the excellent mechanical properties of SRG electrolyte—1.15 MPa breaking stress and 971% breaking strain—enabled the fabrication of flexible LFP||Li pouch cells that underwent stable cycling for 220 cycles at 0.5 C while exhibiting resilience to bending and cutting.

More recently, Gohy and Jia et al.⁷³ developed a dynamic SRG electrolyte containing an α -CD-PEO PR (PEO with $M_w = 35,000$ Da and

100 threaded α -CDs), a tetra-arm boronated single-ion dynamic crosslinker, and 1-ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl)imide (EMIMTFSI)/LiTFSI ionic liquid (Figure 9g). By fine-tuning the molar ratio of ionic liquid to dynamic crosslinker, they reported an optimized ionic conductivity of $2.21 \times 10^{-3} \text{ S cm}^{-1}$ with a Li^+ transfer number of 0.45 at 20 °C. This SRG electrolyte showed thermally stability up to 300 °C and supported stable cycling of a Li||Li symmetrical cells and an NMC622||Li full cell at 20 °C (Figure 9h).

3. MIPs as Electrode Binders

Electrode binder, which typically constitutes 2–30 wt% of the electrode materials depending on the electrode type, provides adhesion between active electrode particles, conductive additives, and the current collector, and also plays crucial roles in the electrochemical redox processes.^{74–77} However, the use of MIPs as electrode binders has been less explored compared to their use as electrolytes.

The pioneering work on MIP binders was reported by Choi and Coskun et al. in 2017.²⁷ They aimed to leverage the excellent mechanical adaptability of SRMs to tackle the pulverization

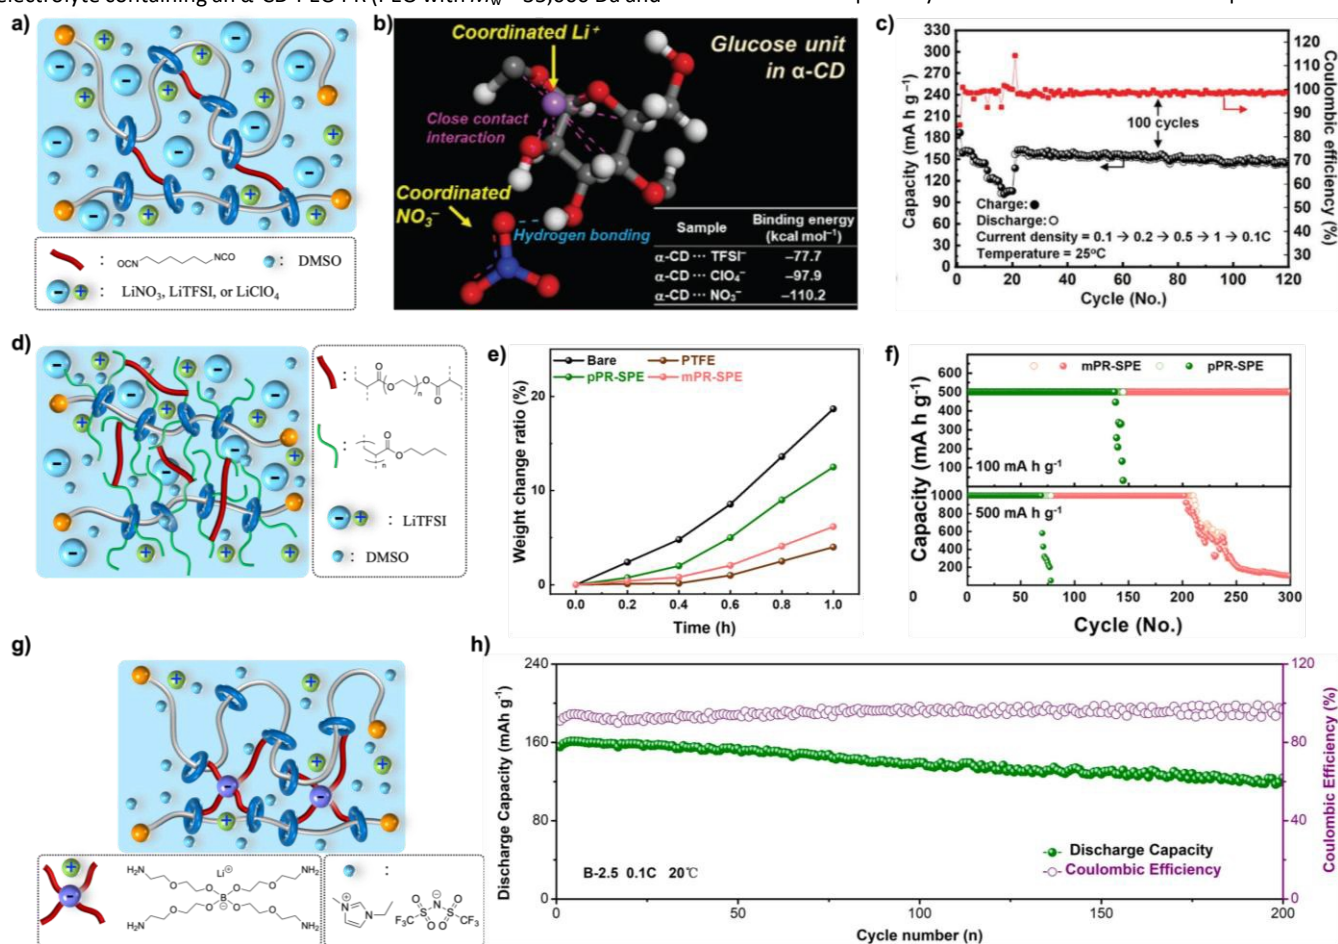


Figure 9 a) SRG electrolytes containing different salts. b) Interaction of α -CD unit with Li^+ cation and salt anions in the SRG electrolytes. c) Performance of a full LFP||Li battery using a SRG electrolyte. d) SRG electrolyte comprising of copolymerized poly(*n*-butyl acrylate) and PEO diacrylate macrolinker through acrylate-functionalized α -CD (mPR-SPE). e) the weight change of a bare Li metal, and ones coated with PTFE, SRG electrolyte containing unmodified CD (pPR-SPE) or mPR-SPE. f) Comparison of a Li|| O_2 full battery performance using pPR-SPE and mPR-SPE. g) SRG electrolyte crosslinked using a single-ion tetra-arm linker, and h) its performance in an NMC622||Li full battery. b) and c) are reproduced from reference [70] with permission from Wiley, copyright 2021, e) and f) are reproduced from reference [71], and f) is reproduced from reference [73] with permission from Wiley, copyright 2021.



challenges of high-energy density silicon (Si) anodes, which undergo large volume change (300–400%) during the charging/discharging cycles (Figure 10a). An α -CD-PEO PR (PEO with $M_w \approx 20,000$ Da and hydroxypropyl α -CDs) was used to crosslink poly(acrylic acid) (PAA, $M_w = 450,000$ Da), yielding a partially crosslinked SRM that was soluble and amendable to wet electrode processing. The SRM showed a twofold improvement in mechanical ductility (390% vs 37% rupture strain) compared with the pure PPA polymer. Subsequent electrode fabrication employing Si microparticle, SRM, and super P in a mass ratio of 8:1:1 yielded a Si anode with an areal loading of ~ 1 mg·cm⁻². A fabricated half-cell (2.67 mAh·cm⁻²) with Li as the counter electrode achieved 91% capacity retention after 150 cycles at 0.64 mA·cm⁻² (0.2C). By contrast, a PAA binder afforded only 48% capacity retention after 50 cycles. Further testing of a full battery pairing a lithium nickel cobalt aluminium oxides (NCA) cathode (2.88 mA·cm⁻²) at a negative-to-positive electrode capacity ratio (N/P) of 1.15 demonstrated 98% capacity retention after 50 cycles at 0.62 mA·cm⁻² (0.2C), with an average CE of 99.92%. Post-cycling analysis of Si anode revealed less pulverization and a thinner residual SEI layer

than the PAA counterpart (Figure 10b). Choi and Coskun, together with Char et al.⁷⁸ later adapted this SRM electrode binder to a commercial carbon-coated silicon monoxide (c-SO_x, x $\sim$ 1) electrodes, which typically present poor interaction with conventional polar polymer binders. Through strong π - π stacking, c-SO_x was blended with a hydroxylated pyrene, whose hydrogen bonding interaction with PAA facilitated dispersion and fabrication of this commercial c-SO_x electrode material (2.3–2.5 mg·cm⁻²). Full cells in pairing with NCA cathodes (N/P = 1.1) retained 82.5% capacity after 150 cycles at 0.5 C (19.4 mg·cm⁻² NCA), and 77.7% capacity after 60 cycles at 0.5 C (27.8 mg·cm⁻² NCA).

In a similar attempt to address the pulverization challenges of Si anodes, Liang, Yan and Yue et al.⁷⁹ reported a MIP binder that combines a PAA and an [an]daisy chain-based MIP. The MIP was prepared by performing the [an]daisy chain followed by attachment of a supramolecular crosslinking unit containing quadruple hydrogen bonding. Blended with PAA at 5 wt%, this MIP binder, combined with super P and Si particle, was used to fabricate the electrodes (mass

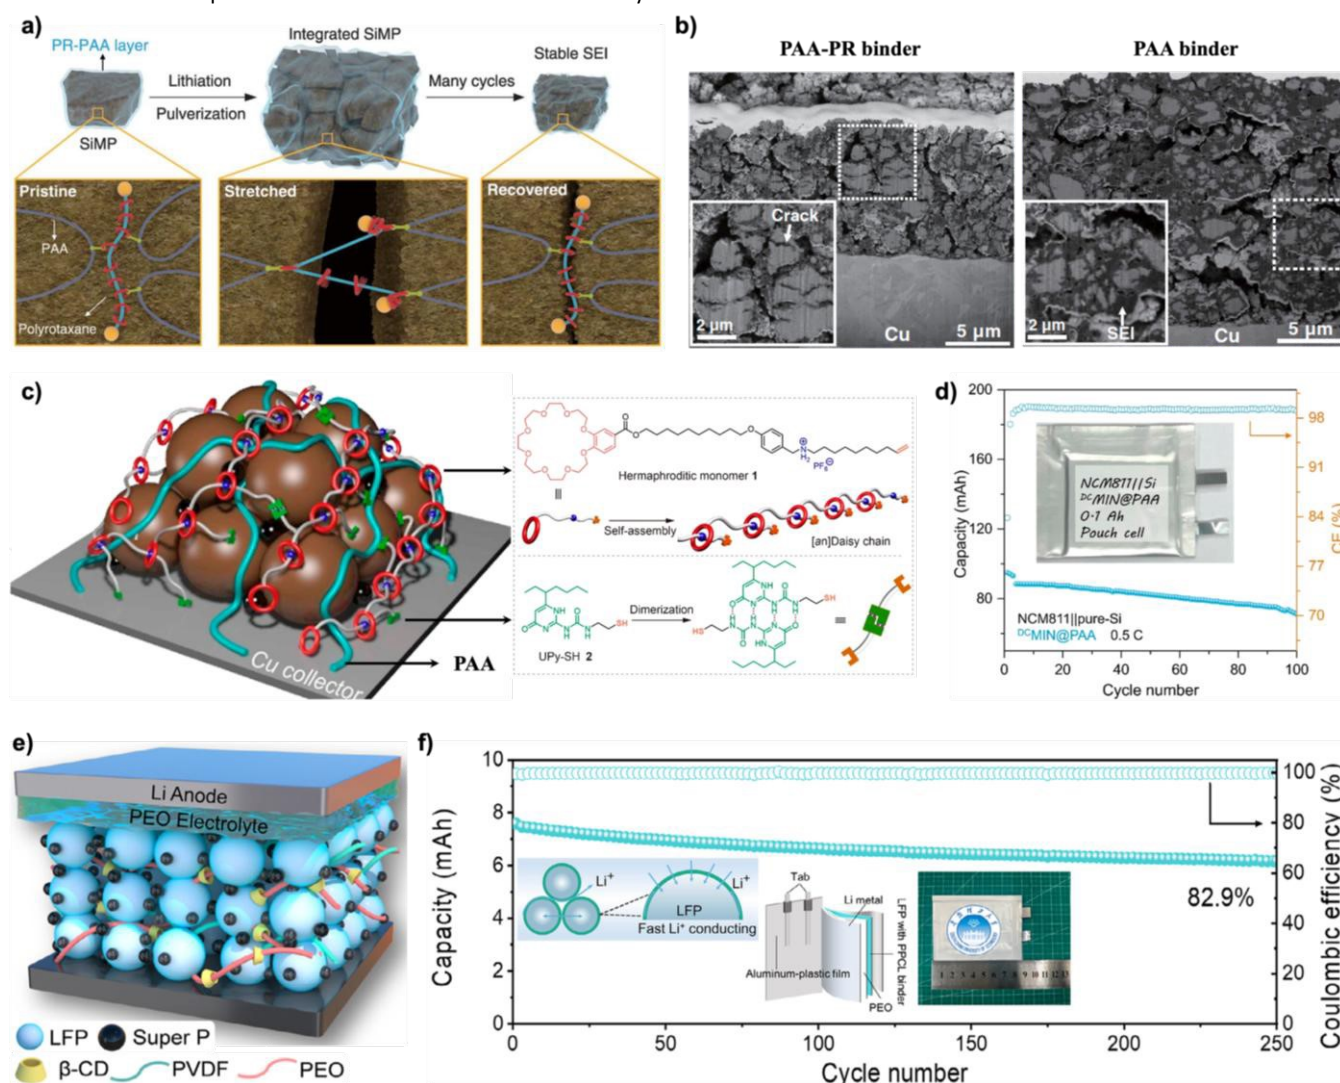


Figure 10 a) Mitigation of pulverization in the Si micro-particle (SiMP) anode during the battery cycling through the use of mechanically adaptive PR-PAA binder. b) Cross-sectional SEM images of SiMP anode after cycling using PR-PAA and PAA binders (after the 10th delithiation. Si loading, 0.70 mg·cm⁻²; 0.2 C rate. c) Schematic of Si anode material fabricated using a novel MIP binder consisting of supramolecular crosslinked [an]daisy chains, and d) the cycling performance of a fabricated 100 mAh pouch cell. e) Illustrated full battery containing hybrid PVDF-PR electrode binder, and f) corresponding cycling performance of a fabricated pouch cell. The hybrid binder was indicated to facilitate the Li⁺ transport at the electrode-electrolyte interface. a) and b) are reproduced from reference [27], c) and d) are reproduced from reference [79] with permission from American Chemical Society, copyright 2024, and e) and f) are reproduced from reference [80] with permission from Wiley, copyright 2025.



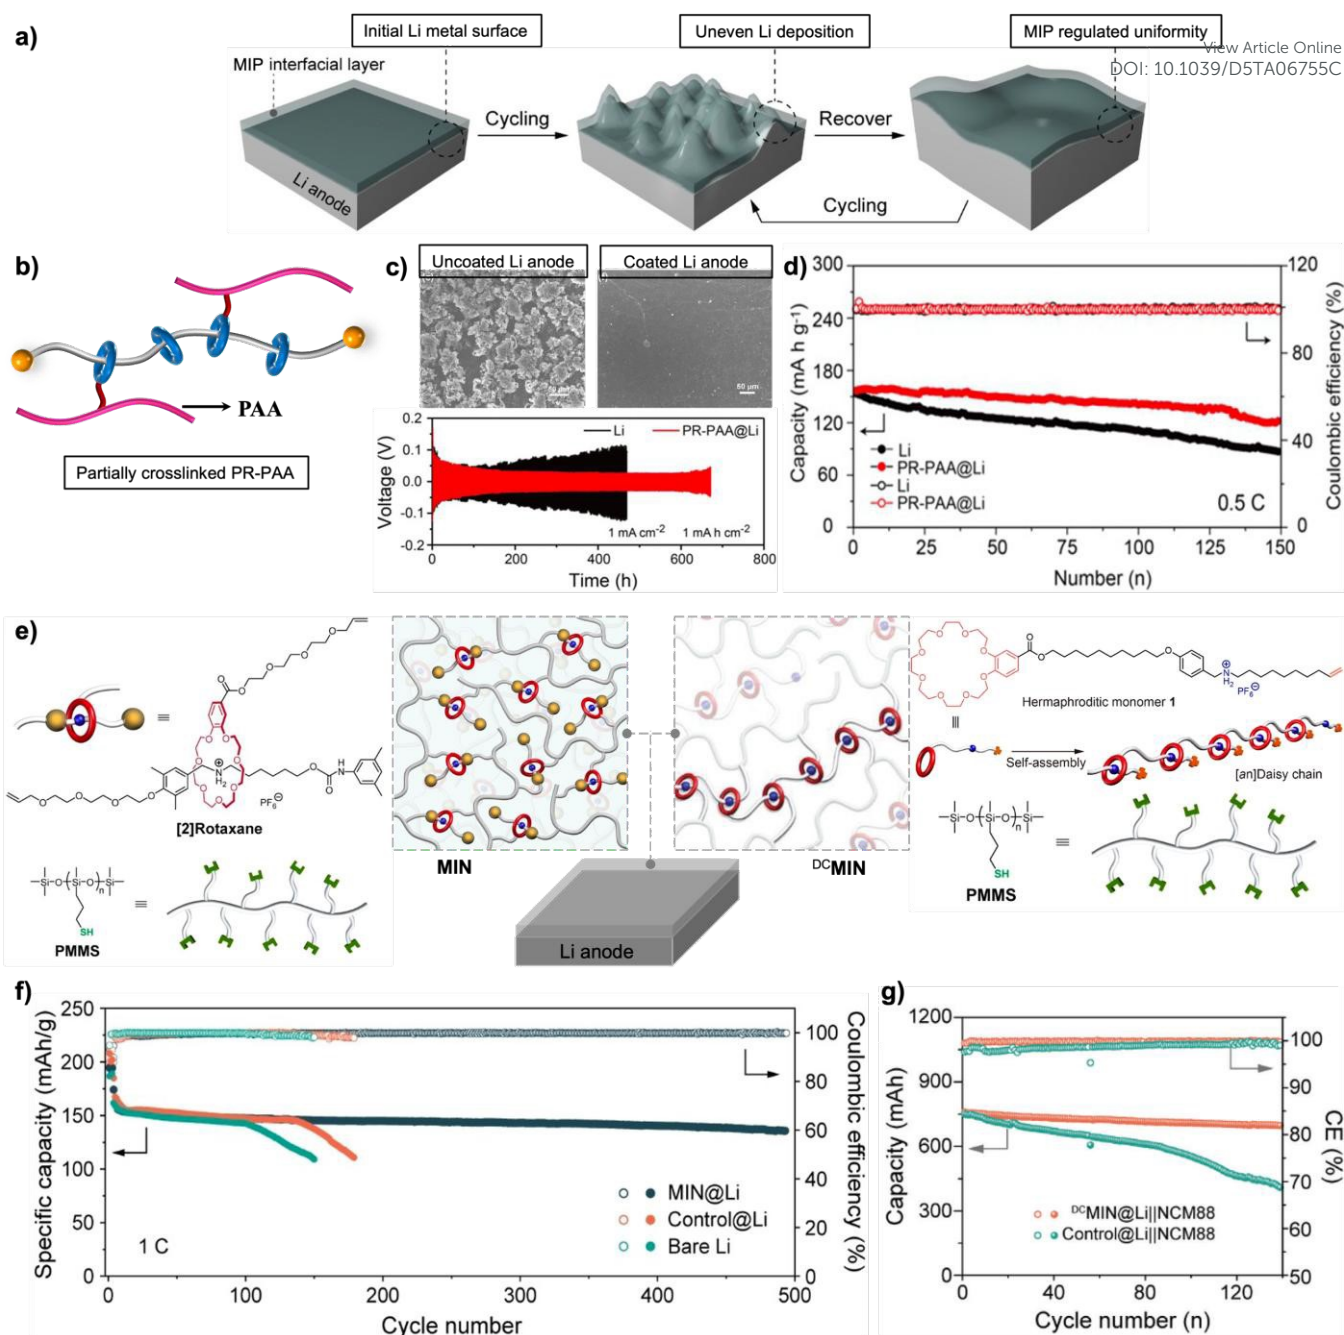


Figure 11 a) MIP coating enabled uniform Li deposition and stable cycling of Li metal anode. b) Partially crosslinked PR-PAA coating polymer. c) PR-PAA coated Li metal anode exhibits more uniform Li deposition and lower overpotential in a Li||Li symmetric cell. d) A Li metal anode coated with PR-PAA polymer showed improved cycling stability compared with a bare one. e) Two novel MIPs consisting of [2]rotaxane or [an]daisy chain crosslinked PDMS networks have been applied as Li metal anode coatings, and both exhibited improved capacity retention in f) a Li||LFP and g) a Li||NCM88 full battery, respectively. a) is reproduced from reference [25] with permission from Wiley, copyright 2022, c) and d) are reproduced from reference [82] with permission from Wiley, copyright 2023, e) is reproduced from references [25] and [26] with permission from Wiley, copyrights 2022 and 2024, respectively. f) and g) are reproduced from references [25] and [26] with permission from Wiley, copyrights 2022 and 2024, respectively.

ratio of 1:2:7) (Figure 10c). Compared to PAA along or a non-interlocked [an]daisy chain, the MIP binder improved electrode adhesion and mechanical resilience. Its use in a Si half-cell (1.1 mg·cm⁻² Si loading) demonstrated 72% capability retention after 300 cycles at 0.5C, with remaining capacity exceeding 1543 mAh·g⁻¹, substantially outperforming controls. Full cells pairing an NCM88 cathode (20 mg·cm⁻²) and a prelithiated Si anode (N/P = 1.1) showed 79.2% capacity retention after 100 cycles at 0.2C; and 87% capacity retention after 200 cycles when a prelithiated Si@Gr anode material was used. In a practical demonstration, a 100 mAh NMC811||Si pouch

cell with this MIP binder achieved 80.4% capacity retention after 100 cycles at 0.5C (Figure 10d).

MIPs were also explored as binders for LFP electrode materials. To address the low ionic conductivity in conventional PVDF binder, Wang and Wang et al.⁸⁰ designed a composite PR binder containing β-CD-PEO (PEO *M_w* = 600,000 Da) PR, PVDF (*M_w* = 100,000 Da), and LiTFSI salt (Figure 10e). Blending this MPI binder with super P and LFP in a mass ratio of 1:1:8 provided LFP electrode with an areal loading of 1.6–10.6 mg·cm⁻². When paired with Li anode, the obtained LFP electrode exhibited an initial capacity of 142 mAh·g⁻¹ and preserved



87.3% capacity after 400 cycles at 1 C. Additionally, a 7.46 mAh pouch cell assembled using this LFP electrode demonstrated 82.9% capacity retention after 250 cycles at 0.2 C (Figure 10f).

4. MIPs as Electrode Coatings

The presence of a stable and robust SEI is crucial for long and stable battery cycling.⁸¹ Formation of such interphase typically occurs in situ during battery operation through electrochemical and/or chemical decomposition of electrolytes. Alternatively, applying an artificial SEI (or electrode coating) in advance can facilitate improved battery performance. Various type of polymers, including commercial and synthesized ones, have been applied as electrode coatings. Detailed polymers and associated electrode systems have been comprehensively reviewed elsewhere.^{4,5} However, MIP-based electrode coatings have been less documented.

In the last decade, Li-metal anode has been regarded as the holy grail of next generation high-energy density electrode materials, with a theoretical specific capacity of 3860 mAh·g⁻¹. However, uneven deposition of Li and the consequent generation of dead Li significantly compromise cycling stability. Applying coatings on the Li-metal anode has demonstrated great potential for performance improvement (Figure 11a). Inspired by this strategy, Guo, Cao and Ye et al.⁸² first applied an SRM coating composed of a PAA chain (M_w = 450,000 Da) crosslinked by an α -CD-PEO PR (PEO with M_w = ~20,000 Da and hydroxypropyl α -CDs), a soluble SRM previously used as binder for Si anode (Figure 11b). A Li-metal anode with a 10 μ m-thick SRM coating exhibited reduced cycling overpotential and dense, even deposition of Li in a Li||Li symmetric cell, contrasting with an uncoated counterpart (Figure 11c). Consequently, full cells assembled with the SRM-coated Li anode exhibited improved performance compared to non-coated cells. For instance, a full cell pairing an LFP cathode (3 mAh·g⁻¹) and a coated Li-metal anode showed an initial capacity of 146 mAh·g⁻¹ and retained 83% capacity after 500 cycles at 1C. Increasing the LFP areal loading to > 3 mAh·cm⁻² resulted in 94.8% capacity retention after 100 cycles at 0.5 C. Similarly, an NMC622 cathode showed an initial capacity of 157 mAh·g⁻¹ and preserved 80% capacity after 100 cycles at 0.5 C (Figure 11d).

Liang and Yan et al.²⁵ designed a novel MIP coating utilizing a PDMS backbone and a crown ether-ammonium-based rotaxane crosslinker. The crosslinked network coating was generated through a post-photocuring method that enables the use of spin coating for precursor application (Figure 11e, left). A 100 nm-thick MIP coating enabled dense and even deposition of Li and facilitated stable cycling of a Li||Li symmetric cell for up to 1500h at 1 mAh·g⁻¹ (1 C). A full cell employing an LFP cathode and a coated Li anode showed an initial capacity of 153 mAh·g⁻¹ and preserved 88% capacity after 500 cycles at 1 C rate (Figure 11f), outperforming both bare Li anode and a counterpart with covalent network coatings. Later, Liang and Yan, together with Yue et al.,²⁶ designed a novel [an]daisy chain crosslinker for coating formation (Figure 11e, right). Similarly, this new MIP coating reduced the overpotential in the Li||Li symmetric cells and improved the cycling stability of LFP||Li full cells (Figure 11g).

5. Discussion and Outlook

View Article Online

DOI: 10.1039/D5TA06755C

The application of emerging MIPs in batteries has demonstrated significant potential and opened new opportunities for enhancing battery performance. Beyond the specific examples reviewed above, MIPs can be employed across a diverse set of electrochemical systems, including but not limited to high-voltage cathodes,⁸³ sodium- and zinc-based electrodes,⁸⁴ and Li-sulfur batteries.⁸⁵ Nevertheless, several challenges must be acknowledged and addressed.

Primarily, this relatively unexplored field—compared to the application of conventional polymer materials—is limited by the synthetic challenges associated with MIPs. Advances in the design and scalable synthesis are essential for their applications in batteries, especially as polymer electrolytes and electrode binders. For electrode coatings, the required thickness of polymer coating is typically ranges from 10 nm to 10 μ m,^{86,87} thus requiring much less materials in these applications.

Second, the integration of MIPs into batteries depends strongly on their topology. Linear or partially crosslinked MIPs with good solubility in solvents can be processed using conventional solution-based fabrication methods, enabling precise control over composition and coating or binder thickness and results in well-defined interface contact. By contrast, processing crosslinked MIPs presents challenges once the networks forms. In particular, an in situ or post-fabrication network curing process is necessary to ensure successful integration of crosslinked MIPs as binders or coatings. In situ network curing methods—where a liquid polymer precursor is polymerized directly on or within the electrode—can substantially improve the interface properties between the electrode and electrolyte. This process enables the polymer network to penetrate pores and conform intimately to the electrode surface and active particles, which results in several key benefits including enhanced interfacial contact, low interfacial resistance and stable and uniform SEI formation.^{88,89} Direct use of crosslinked MIPs as polymer electrolytes, (or as membranes to insulate anode and cathode) seems to be more straightforward. However, when using crosslinked MIPs as solid-state electrolytes, achieving effective contact between the electrolyte and electrode remains challenging. Strategies such as in situ curing and employing MIPs as catholytes and anolytes can help mitigate this challenge.

Improving the ionic conductivity of solid-state polymer electrolytes stands as a long-term challenge, as is the case for MIP solid-state electrolytes. Previous results have demonstrated the potential of achieving relatively high ionic conductivity (> 10⁻⁴ S·cm⁻¹) at near room temperature using MIPs,^{50,63,64} comparable to the ionic conductivity of typical liquid electrolytes when infiltrated into membranes. However, a deep understanding of how the mechanical bond motif and associated polymer segmental motion affects ion transport is still lacking. On the other hand, in MIP gel electrolytes, the ionic conductivity can be enhanced by increasing the fraction of plasticizer, albeit at the cost of compromised modulus and mechanical strength. Balanced mechanical strength and ionic conductivity is critical for optimal battery performance, yet the



detailed mechanisms underpinning their combined effects remain to be fully elucidated. Finally, the electrochemical compatibility of MIP electrolytes with both anode and cathode needs to be considered, and compositions of polymer backbone and mechanical bond should be pre-evaluated when incorporated into the batteries.

When used as electrode binders, MIPs must provide adhesion both between active material particles and to substrate/current collector. Minimizing binder content while maintaining these adhesion functions is ideal to maximize the loading of active materials and the resulting energy density. Similar to MIP electrolytes, the electrochemical compatibility of MIP binders with electrode materials depends on the choice of polymer backbones and mechanical bond motifs and thus requires thorough evaluation. Additionally, binder materials should ideally swell but not dissolve in liquid electrolytes, especially for the linear or partially crosslinked MIP binders.

MIP coatings for electrodes should also exhibit electrochemically compatibility and remain insoluble in liquid electrolytes. Some studies have indicated that coatings can be ion-philic but solvent-phobic,⁹⁰ thereby facilitating ion transfer while mitigating parasitic solvent decomposition at the electrode interface. While MIP coatings have primarily been applied to Li-metal anodes as artificial SEIs, their application as cathode-electrolyte interphases (CEIs)⁹¹ shares some similarities.

To conclude, despite challenges in their designing and synthesis, MIPs have demonstrated great potential for enhancing battery performance through their roles as polymer electrolytes, electrode binders, and coatings.

Conflicts of interest

There are no conflicts to declare.

Data availability

All data discussed in this review are taken from previously published sources, which are appropriately cited in the article.

Acknowledgements

This study is supported by startup grant offered by the Chemistry Department at the University of Waterloo and by the funding from Natural Sciences and Engineering Research Council of Canada (NSERC).

References

- 1 A. Manthiram, *ACS Cent. Sci.*, 2017, **3**, 1063–1069.
- 2 J. Lopez, D. G. Mackanic, Y. Cui and Z. Bao, *Nat. Rev. Mater.*, 2019, **4**, 312–330.
- 3 D. Mecerreyes, N. Casado, I. Villaluenga and M. Forsyth, *Macromolecules*, 2024, **57**, 3013–3025.
- 4 Z. Yu, Y. Cui and Z. Bao, *Cell Rep. Phys. Sci.*, 2020, **1**, 100119.

- 5 Z. Huang, H. Lyu, L. C. Greenburg, Y. Cui and Z. Bao, *Nat. Energy*, 2025, **10**, 811–823. DOI: 10.1039/D5TA06755C
- 6 X. Zhang, J.-C. Daigle and K. Zaghbi, *Materials*, 2020, **13**, 2488.
- 7 Z. Song, F. Chen, M. Martinez-Ibañez, W. Feng, M. Forsyth, Z. Zhou, M. Armand and H. Zhang, *Nat. Commun.*, 2023, **14**, 4884.
- 8 F. Zou and A. Manthiram, *Adv. Energy Mater.*, 2020, **10**, 2002508.
- 9 Y. Shi, X. Zhou and G. Yu, *Acc. Chem. Res.*, 2017, **50**, 2642–2652.
- 10 H. Yuan, J.-Q. Huang, H.-J. Peng, M.-M. Titirici, R. Xiang, R. Chen, Q. Liu and Q. Zhang, *Adv. Energy Mater.*, 2018, **8**, 1802107.
- 11 S. Li, Y.-M. Liu, Y.-C. Zhang, Y. Song, G.-K. Wang, Y.-X. Liu, Z.-G. Wu, B.-H. Zhong, Y.-J. Zhong and X.-D. Guo, *J. Power Sources*, 2021, **485**, 229331.
- 12 J. F. Stoddart, *Chem. Soc. Rev.*, 2009, **38**, 1802.
- 13 L. Chen, X. Sheng, G. Li and F. Huang, *Chem. Soc. Rev.*, 2022, **51**, 7046–7065.
- 14 M. K. Beyer, *J. Chem. Phys.*, 2000, **112**, 7307–7312.
- 15 B. Lee, Z. Niu and S. L. Craig, *Angew. Chem. Int. Ed.*, 2016, **55**, 13086–13089.
- 16 G. De Bo, *Chem. Sci.*, 2018, **9**, 15–21.
- 17 L. F. Hart, J. E. Hertzog, P. M. Rauscher, B. W. Rowe, M. M. Tranquilli and S. J. Rowan, *Nat. Rev. Mater.*, 2021, **6**, 508–530.
- 18 Y. Noda, Y. Hayashi and K. Ito, *J. Appl. Polym. Sci.*, 2014, **131**, app.40509.
- 19 R. Ikura, Y. Ikemoto, M. Osaki, H. Yamaguchi, A. Harada and Y. Takashima, *Polymer*, 2020, **196**, 122465.
- 20 D. Aoki and T. Takata, *Polymer*, 2017, **128**, 276–296.
- 21 L. F. Hart, W. R. Lenart, J. E. Hertzog, J. Oh, W. R. Turner, J. M. Dennis and S. J. Rowan, *J. Am. Chem. Soc.*, 2023, **145**, 12315–12323.
- 22 N. Sugihara, K. Nishimura, H. Nishino, S. Kanehashi, K. Mayumi, Y. Tominaga, T. Shimomura and K. Ito, *Electrochimica Acta*, 2017, **229**, 166–172.
- 23 Y.-C. Lin, K. Ito and H. Yokoyama, *Polymer*, 2018, **136**, 121–127.
- 24 L. Imholt, T. S. Dörr, P. Zhang, L. Ibing, I. Cekic-Laskovic, M. Winter and G. Brunklaus, *J. Power Sources*, 2019, **409**, 148–158.
- 25 J. Zhao, M. Hong, Z. Ju, X. Yan, Y. Gai and Z. Liang, *Angew. Chem. Int. Ed.*, 2022, **61**, e202214386.
- 26 Z. Shi, Y. Wang, X. Yue, J. Zhao, M. Fang, J. Liu, Y. Chen, Y. Dong, X. Yan and Z. Liang, *Adv. Mater.*, 2024, **36**, 2401711.
- 27 S. Choi, T. Kwon, A. Coskun and J. W. Choi, *Science*, 2017, **357**, 279–283.
- 28 X. Xiong, Y. Chen, Z. Wang, H. Liu, M. Le, C. Lin, G. Wu, L. Wang, X. Shi, Y.-G. Jia and Y. Zhao, *Nat. Commun.*, 2023, **14**, 1331.
- 29 Y. Jiang, Z. Zhang, Y.-X. Wang, D. Li, C.-T. Coen, E. Hwaun, G. Chen, H.-C. Wu, D. Zhong, S. Niu, W. Wang, A. Saberi, J.-C. Lai, Y. Wu, Y. Wang, A. A. Trotsyuk, K. Y. Loh, C.-C. Shih, W. Xu, K. Liang, K. Zhang, Y. Bai, G. Gurusankar, W. Hu, W. Jia, Z. Cheng, R. H. Dauskardt, G. C. Gurtner, J. B.-H. Tok, K. Deisseroth, I. Soltesz and Z. Bao, *Science*, 2022, **375**, 1411–1417.
- 30 D. Xia, P. Wang, X. Ji, N. M. Khashab, J. L. Sessler and F. Huang, *Chem. Rev.*, 2020, **120**, 6070–6123.
- 31 R. P. S, V. Prasannavenkadesan, V. Katiyar and A. S. Achalkumar, *RSC Appl. Polym.*, 2025, **3**, 499–531.
- 32 C. Y. Son and Z.-G. Wang, *J. Chem. Phys.*, 2020, **153**, 100903.
- 33 L. Long, S. Wang, M. Xiao and Y. Meng, *J. Mater. Chem. A*, 2016, **4**, 10038–10069.
- 34 Y. Shao, H. Gudla, J. Mindemark, D. Brandell and C. Zhang, *Acc. Chem. Res.*, 2024, **57**, 1123–1134.
- 35 H. Gudla, A. Hockmann, D. Brandell and J. Mindemark, *ACS Appl. Polym. Mater.*, 2025, **7**, 4716–4724.
- 36 S. Mogurampelly, O. Borodin and V. Ganesan, *Annu. Rev. Chem. Biomol. Eng.*, 2016, **7**, 349–371.



- 37 J. Wang, S. Li, Q. Zhao, C. Song and Z. Xue, *Adv. Funct. Mater.*, 2021, **31**, 2008208.
- 38 A. J. Tsamopoulos and Z.-G. Wang, *ACS Macro Lett.*, 2024, **13**, 322–327.
- 39 G. Foran, J. Chidiac, C. St-Antoine, P. Nicolle, L. Caradant, A. Prébé and M. Dollé, *Macromolecules*, 2025, **58**, 6820–6828.
- 40 N. Molinari, J. P. Mailloa and B. Kozinsky, *Chem. Mater.*, 2018, **30**, 6298–6306.
- 41 Z. Xue, D. He and X. Xie, *J. Mater. Chem. A*, 2015, **3**, 19218–19253.
- 42 J. Li, J. Li, L. Wan and Z. Li, *Soft Matter*, 2025, **21**, 3410–3424.
- 43 J. Feng, L. Wang, Y. Chen, P. Wang, H. Zhang and X. He, *Nano Conver.*, 2021, **8**, 2.
- 44 M. A. Webb, Y. Jung, D. M. Pesko, B. M. Savoie, U. Yamamoto, G. W. Coates, N. P. Balsara, Z.-G. Wang and T. F. I. Miller, *ACS Cent. Sci.*, 2015, **1**, 198–205.
- 45 L. Yang, D. Wei, M. Xu, Y. Yao and Q. Chen, *Angew. Chem. Int. Ed.*, 2014, **53**, 3631–3635.
- 46 L. Yang, X. Fu, T. Chen, L. Pan, P. Ji, Y. Yao and Q. Chen, *Chem. – Eur. J.*, 2015, **21**, 6346–6349.
- 47 X.-B. Fu, L.-Y. Yang, J.-Q. Ma, G. Yang, Y.-F. Yao and Q. Chen, *Polymer*, 2016, **105**, 310–317.
- 48 Y. Okumura and K. Ito, *Adv. Mater.*, 2001, **13**, 485–487.
- 49 K. Hashimoto, T. Shiwaiku, H. Aoki, H. Yokoyama, K. Mayumi and K. Ito, *Sci. Adv.*, 2023, **9**, eadi8505.
- 50 B. Kim, E. Lee and J.-H. Seo, *ACS Macro Lett.*, 2024, 1463–1468.
- 51 R.-D. Wang, Y.-F. Zhang, X.-L. Han, X.-Y. Fan, J. Tian, Y.-K. Gao, T.-T. You and P.-G. Yin, *ACS Appl. Polym. Mater.*, 2024, **6**, 15124–15135.
- 52 R.-D. Wang, Y.-F. Zhang, X.-L. Han, Y.-K. Gao, T.-T. You and P.-G. Yin, *Eur. Polym. J.*, 2025, **230**, 113893.
- 53 W. Xue, F. Ahangaran, H. Wang, P. Theato and Y.-J. Cheng, *Macromol. Rapid Commun.*, DOI: 10.1002/marc.202500207.
- 54 S. Sen, S. Malunavar and A. J. Bhattacharyya, *J. Phys. Chem. B*, 2016, **120**, 10153–10161.
- 55 A. Hosseinioun, P. Nürnberg, M. Schönhoff, D. Diddens and E. Paillard, *RSC Adv.*, 2019, **9**, 27574–27582.
- 56 N. Sugihara, Y. Tominaga, T. Shimomura and K. Ito, *Electrochimica Acta*, 2015, **169**, 433–439.
- 57 T. Moriyasu, T. Sakamoto, N. Sugihara, Y. Sasa, Y. Ota, T. Shimomura, Y. Sakai and K. Ito, *Polymer*, 2013, **54**, 1490–1496.
- 58 H. Nishino, C. Liu, S. Kanehashi, K. Mayumi, Y. Tominaga, T. Shimomura and K. Ito, *Ionics*, 2020, **26**, 255–261.
- 59 L. Imholt, D. Dong, D. Bedrov, I. Cekic-Laskovic, M. Winter and G. Brunklaus, *ACS Macro Lett.*, 2018, **7**, 881–885.
- 60 *Beilstein J. Org. Chem.*, 2014, **10**, 2573–2579.
- 61 C. A. Angell, C. Liu and E. Sanchez, *Nature*, 1993, **362**, 137–139.
- 62 Y. Wang, Z. Li, H. Xu, Q. Wang, W. Peng, S. Chi, C. Wang, J. Wang and Y. Deng, *ACS Appl. Mater. Interfaces*, 2023, **15**, 31552–31560.
- 63 S. Yan, H. Jia, Y. Li, Z. Chen, R. Lyons, Z. He, Y. Zhang, C. Liu, C.-A. Fustin and J.-F. Gohy, *Chem. Eng. J.*, 2024, **495**, 153874.
- 64 P. Ding, L. Wu, Z. Lin, C. Lou, M. Tang, X. Guo, H. Guo, Y. Wang and H. Yu, *J. Am. Chem. Soc.*, 2023, **145**, 1548–1556.
- 65 W. Wang and P. Alexandridis, *Polymers*, 2016, **8**, 387.
- 66 P. Yao, H. Yu, Z. Ding, Y. Liu, J. Lu, M. Lavorgna, J. Wu and X. Liu, *Front. Chem.*, DOI:10.3389/fchem.2019.00522.
- 67 J. Li, Z. Wang, Q. Tong, L. Yang, M. Zhu, H. Lin, F. Gao and J. Weng, *Ionics*, 2022, **28**, 3623–3634. DOI: 10.1039/D5TA06755C
- 68 Y. He, Y. Li, Q. Tong, J. Zhang, J. Weng and M. Zhu, *ACS Appl. Mater. Interfaces*, 2021, **13**, 41593–41599.
- 69 H. Xia, G. Xu, X. Cao, C. Miao, H. Zhang, P. Chen, Y. Zhou, W. Zhang and Z. Sun, *Adv. Mater.*, 2023, **35**, 2301996.
- 70 J. Seo, G. Lee, J. Hur, M. Sung, J. Seo and D. Kim, *Adv. Energy Mater.*, 2021, **11**, 2102583.
- 71 B. Kim, M.-C. Sung, G.-H. Lee, B. Hwang, S. Seo, J.-H. Seo and D.-W. Kim, *Nano-Micro Lett.*, 2025, **17**, 31.
- 72 X. Deng, J. Chen, X. Jia, X. Da, Y. Zhao, Y. Gao, Y. Gao, X. Kong, S. Ding and G. Gao, *Angew. Chem. Int. Ed.*, 2024, e202410818.
- 73 S. Yan, J. Liu, Z. He, H. Jia, Z. Chen, Y. Zhang and J.-F. Gohy, *Angew. Chem. Int. Ed.*, 2025, **64**, e202503307.
- 74 S. Bandyopadhyay and B. Nandan, *Energy Storage Mater.*, 2025, **78**, 104233.
- 75 Y. Ding, Y. Wang, C. Liu, J. Deng, S. Qu, Y. Wang, R. Bai, Y. Liu, G. Liu, C. Yue, W. Yu, Z. Zhang and X. Yan, *Angew. Chem. Int. Ed.*, 2025, **64**, e202510140.
- 76 D.-Y. Han, I. K. Han, J. Y. Kwon, S. Nam, S. Kim, Y. Song, Y. Kim, Y. S. Kim, S. Park and J. Ryu, *Adv. Sci.*, 2025, **12**, 2417143.
- 77 J. Kang, J. Kwon, D.-Y. Han, S. Park and J. Ryu, *Appl. Phys. Rev.*, DOI:10.1063/5.0182553.
- 78 Y. Cho, J. Kim, A. Elabd, S. Choi, K. Park, T. Kwon, J. Lee, K. Char, A. Coskun and J. W. Choi, *Adv. Mater.*, 2019, **31**, 1905048.
- 79 Z. Liu, Y. Wang, G. Liu, X. Yue, Z. Shi, Y. Tan, J. Zhao, Y. Lei, X. Yan and Z. Liang, *J. Am. Chem. Soc.*, 2024, **146**, 34491–34500.
- 80 H. Liu, S. Wang, W. Kong, Y. Liu and H. Wang, *Angew. Chem. Int. Ed.*, 2025, **64**, e202507579.
- 81 H. Adenusi, G. A. Chass, S. Passerini, K. V. Tian and G. Chen, *Adv. Energy Mater.*, 2023, **13**, 2203307.
- 82 R. Gao, H. Yang, C. Wang, H. Ye, F. Cao and Z. Guo, *Angew. Chem. Int. Ed.*, 2021, **60**, 25508–25513.
- 83 W. Li, B. Song and A. Manthiram, *Chem. Soc. Rev.*, 2017, **46**, 3006–3059.
- 84 L. P. Wang, L. Yu, X. Wang, M. Srinivasan and Z. J. Xu, *J. Mater. Chem. A*, 2015, **3**, 9353–9378.
- 85 L. Tang, H. Peng, J. Kang, H. Chen, M. Zhang, Y. Liu, D. H. Kim, Y. Liu and Z. Lin, *Chem. Soc. Rev.*, 2024, **53**, 4877–4925.
- 86 J. Lopez, A. Pei, J. Y. Oh, G.-J. N. Wang, Y. Cui and Z. Bao, *J. Am. Chem. Soc.*, 2018, **140**, 11735–11744.
- 87 S. Stalin, M. Tikekar, P. Biswal, G. Li, H. E. N. Johnson, Y. Deng, Q. Zhao, D. Vu, G. W. Coates and L. A. Archer, *Nano Lett.*, 2020, **20**, 5749–5758.
- 88 S. Li, H. Gao, J. Tan, Z. Qiu, X. Guo and Y. Yan, *ACS Appl. Mater. Interfaces*, 2025, **17**, 55338–55346.
- 89 H. Wu, G. Yu, L. Pan, N. Liu, M. T. McDowell, Z. Bao and Y. Cui, *Nat. Commun.*, 2013, **4**, 1943.
- 90 Z. Huang, J.-C. Lai, S.-L. Liao, Z. Yu, Y. Chen, W. Yu, H. Gong, X. Gao, Y. Yang, J. Qin, Y. Cui and Z. Bao, *Nat. Energy*, 2023, **8**, 577–585.
- 91 S. P. Kühn, K. Edström, M. Winter and I. Cekic-Laskovic, *Adv. Mater. Interfaces*, 2022, **9**, 2102078.



Review Manuscript

Table 1 Summary of MIP polymer electrolytes with corresponding electrochemical and mechanical properties. ^a Indicated with host molecule and guest polymer chain. HyPr- α -CD refers to hydroxypropyl modified - α -CD; Me- α -CD denotes methylated α -CDs; HDI represent hexamethylene diisocyanate, and MDI means methylene diphenyl diisocyanate. ^b PC indicates propylene carbonate; EMIES means 1-ethyl-3-methylimidazolium ethyl sulfate, and EMITFSI is 1-ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl)imide; G3 is triethylene glycol dimethyl ether. ^c $\sigma_{\max}$ refers to maximum tensile stress, $\epsilon_{\max}$ indicate maximum tensile strain, and E means Young's modulus. ^d Compression strain.

Electrolyte Type	^a Polymer Design	Salt (and ^b Plasticizer)	σ (S·cm ⁻¹)	E_a (kJ·mol ⁻¹)	t^+	^c Mechanical Property ($\sigma_{\max}$, $\epsilon_{\max}$ and E)	Ref
Solid-state	α -CD-PEO (Pseudo-PR)	LiAsF ₆	5.6×10^{-9} (30 °C)	75.1	NA	NA NA NA	45
	β -CD-PEO (Pseudo-PR)	LiAsF ₆	8.3×10^{-9} (25 °C)	123.2	NA	NA NA NA	46
	β -CD-PEO (Pseudo-PR)	NaAsF ₆	5.5×10^{-7} (25 °C)	58.2	NA	NA NA NA	46
	β -CD-PEO-co-PPO (Pseudo-PR)	LiAsF ₆	3.2×10^{-5} (25 °C)	NA	NA	NA NA NA	47
	β -CD-PPO (Pseudo-PR)	LiAsF ₆	9.5×10^{-9} (25 °C)	NA	NA	NA NA NA	47
	HyPr- α -CD-PEO + HDI (SRM)	LiClO ₄	$\sim 10^{-7}$ (60 °C)	23.2	NA	16.6 MPa 200% 570MPa	47
	α -CD-PEO + HDI (SRM)	Li(NTf ₂)	$\sim 10^{-5}$ (30 °C)	9.4	NA	15.6 MPa 1600% ~ 10 MPa	49
	α -CD-PEO + MDI and HDI (SRM)	LiNO ₃	3.4×10^{-3} (25 °C)	13.3	0.63	NA NA NA	50
	HyPr- α -CD-PEO + PEO macrolinker (SRM)	LiTFSI	2.7×10^{-5} (30 °C)	NA	NA	4.9 MPa 552% ~ 12.5 MPa	51
Gel	Me- α -CD-PEO + Divinyl sulfone (SRG)	LiTFSI+PC	2.9×10^{-3} (25 °C)	6.8	NA	NA ^d 51.5% 14.8 kPa	56
	HyPr- α -CDs-PEO + Diglycidyl ether (SRG)	EMIES	$1.7\text{--}3.2 \times 10^{-3}$ (20 °C)	NA	NA	NA NA 15–30 kPa	57
	HyPr- α -CDs-PEO + Divinyl sulfone (SRG)	LiTFSI +EMITFSI	$2.66\text{--}4.31 \times 10^{-3}$ (30 °C)	2.8–3.0	NA	NA NA 8.4–60.5 kPa	22
	α -CDs-PEO + Divinyl sulfone (SRG)	Mg(TFSI) ₂ +G3	1.73×10^{-3} (25 °C)	1.35	NA	0.05 MPa 300% 20 kPa	58



Table 2 Application of MIP electrolyte in various of full batteries. ^a PCL-*g*- α -CD means PCL grafted α -CD, 18C6 refers to 18-crown-6-ether, and HDI denotes hexamethylene diisocyanate. ^b EC, EMC, and DEC refer to ethylene carbonate, ethyl methyl carbonate, and diethyl carbonate, respectively; DDN electrolyte: LiTFSI dissolved in a 1:1 (v:v) mixture of 1,3-dioxolane (DOL) and 1,2-dimethoxyethane (DME), with a 1 wt% addition of LiNO₃; EMIMTFSI refers to 1-ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl)imide. ^c Paired cathode with indicated areal loading and cut-off voltage for battery cycling.

Electrolyte Type	^a Polymer Design	^b Salt (and Plasticizer)	σ (S·cm ⁻¹)	t^+	LSV onset vs. Li/Li ⁺	^c Full Battery	Cycling Stability	Ref
Solid-state	γ -CD-PEO (Pseudo-PR)	LiTFSI	$\sim 10^{-4}$ (100 °C)	0.34 (70 °C)	NA	Li LFP (1.2 mg·cm ⁻²) (2.5–3.8V)	95% retention after 200 cycles at 1C, average CE=99.4% (60 °C)	59
	PCL- <i>g</i> - α -CD-PEO (PR polymer-in-salt)	LiFSI	4.89×10^{-4} (30 °C)	0.64 (30 °C)	4.7 V (10 mV·s ⁻¹ , 30 °C)	Li NCM811 (3–4 mg·cm ⁻²) (3.0–4.3 V)	80% retention after 100 cycles and 68% retention after 150 cycles at 0.2C, average CE=99% (30 °C)	62
	α -CD-PEO + PEO linker (SRM)	LiClO ₄	7.25×10^{-4} (60 °C)	0.54 (60 °C)	> 4.8 V (1 mV·s ⁻¹ , 60 °C)	Li LFP (1.0 mg·cm ⁻²) (3.0–3.8V)	56% retention after 90 cycles at 0.1C (60 °C)	63
	18C6-PEO + HDI (Crosslinked PR)	LiTFSI	3.48×10^{-4} (25 °C)	0.41 (25 °C)	> 4.8 V (1 mV·s ⁻¹ , 25 °C)	Li LFP (2–3 mg·cm ⁻²) (2.5–4.0V)	96.5% retention after 250 cycles at 0.5C (25 °C)	64
Gel	α -CD-PEO + PVDF-HFP (pseudo-PR composite)	LiPF ₆ + EC/EMC/DEC	1.73×10^{-4} (25 °C)	0.69 (25 °C)	5.25 V (1 mV·s ⁻¹ , 25 °C)	Li LFP (1.5–1.7 mg·cm ⁻²) (2.5–4.0V)	No obvious decay after 40 cycles at 1C (25 °C 55 °C or 80 °C)	67
						Li NMC532 (loading NA)	86% retention after 300 cycles at 0.5C rate (25 °C)	67
	α -CD-PEO + PVDF-HFP (pseudo-PR composite)	LiTFSI + DDN	8.3×10^{-4} (25 °C)	0.51 (25 °C)	> 4.5 V (1 mV·s ⁻¹ , 25 °C)	Li LFP (loading NA) (2.5–3.8V)	99.02% after 100 cycles and 78.8% after 500 cycles at 1C (25 °C)	68
	α -CD-PEO + PAM (pseudo-PR composite)	Zn(OTf) ₂ + H ₂ O	22.4×10^{-3} (25 °C)	0.92 (25 °C)	NA	Zn La-V ₂ O ₅ (1.0 mg·cm ⁻²) (0.4–1.6 V)	90.2% retention after 3500 cycles at 5A/g (25 °C)	69
	α -CD-PEO+HDI (SRG)	LiNO ₃ + DMSO	5.93×10^{-3} (25 °C)	0.71 (25 °C)	4.7 V (10 mV·s ⁻¹ , 25 °C)	Li LFP (2.1 mg·cm ⁻²) (2.5–4.0V)	91.2% retention after 100 cycles at 0.1C, 98.6% CE (25 °C)	70
	α -CD-PEO + PnBA + PEO macrolinker (SRG)	LiNO ₃ + DMSO	2.8×10^{-3} (25 °C)	0.61 (25 °C)	4.8 V (10 mV·s ⁻¹ , 25 °C)	Li O ₂ (500 mAh·g ⁻¹ limit)	>300 cycles at 0.2C rate and 200 cycles at 1C rate (25 °C)	71
	α -CD-PEO + PEO macrolinker (SRG)	LiTFSI + DDN	1.73×10^{-3} (30 °C)	0.71 (30 °C)	4.7 V (1 mV·s ⁻¹ , 25 °C)	Li LFP (2.4–2.6 mg·cm ⁻²) (2.8–4.0V)	89.6% retention after 1000 cycles at 1C, 96.4% retention after 250 cycles at 5C (25 °C)	71
	α -CD-PEO + <i>tetra</i> -arm linker (SRG)	LiTFSI + EMIMTFSI	2.21×10^{-3} (20 °C)	0.45 (20 °C)	4.6 V	Li NMC622 (1.1 mg·cm ⁻²)	92% retention after 300 cycles at 0.1C (20 °C)	73

