

CrossMark  
click for updatesCite this: *RSC Adv.*, 2017, 7, 408

# Eosin Y dye-based porous organic polymers for highly efficient heterogeneous photocatalytic dehydrogenative coupling reaction†

Chang-An Wang,\* Yan-Wei Li, Xue-Li Cheng, Jian-Ping Zhang and Yin-Feng Han\*

Construction of porous organic polymers (POPs) as metal-free heterogeneous organic photocatalysts for highly efficient catalytic organic transformations using visible light remains a key challenge. Herein, we report the "bottom-up" strategy to facilitate synthesis of two Eosin Y dye-based POP frameworks (EY-POPs) for highly efficient heterogeneous organic photocatalysis. Owing to the high BET surface area and the built-in character of the covalently linked catalytic sites of EY-POPs, these photoactive polymers show excellent catalytic activity in photocatalyzing the aza-Henry reaction. The superior utility of the EY-POP-1 polymer in catalysis was demonstrated by the broad scope of the reactants and the high yield of the reaction products. Moreover, the EY-POP-1 polymer shows robust recycling capability with good retention of photoactivity over at least twelve cycles without any significant loss of the catalytic activity (94–98% yield).

Received 12th October 2016  
Accepted 14th November 2016

DOI: 10.1039/c6ra25123d

[www.rsc.org/advances](http://www.rsc.org/advances)

## Introduction

Organic transformations driven by visible light offer a sustainable alternative to many ever-pressing environmental issues. With the aim to exploit photons for synthetic purposes, visible-light photoredox catalysis has recently proven to be a powerful method to perform several organic reactions.<sup>1</sup> Because the majority of organic substrates in these reactions do not readily absorb photons in the visible region, photocatalysts are often required in visible light driven organic reactions. To date, transition-metal-systems, such as ruthenium(II), mainly [Ru(bpy)<sub>3</sub>Cl<sub>2</sub>], or iridium(III) complexes have been applied to photoredox reactions<sup>2</sup> such as radical addition and cycloaddition reactions,<sup>3</sup> aza-Henry reactions,<sup>4</sup> asymmetric alkylation of aldehydes,<sup>5</sup> and other reactions. Recently, organic dyes have been also successfully applied as effective visible light metal-free photoredox organocatalysts.<sup>6</sup> However, like other precious homogeneous catalysis, these homogeneous photocatalysts are generally considered of low efficiency due to the high catalyst loading and the difficulty in separation from the products, which restricts their practical application in large scale. Furthermore, their potential toxicity could lead to detrimental effects on public health and the environment. Accordingly, it is highly desirable to develop robust and reusable heterogeneous photocatalytic systems based on these homogeneous photocatalysts.<sup>7</sup> The ability to recover and reuse such heterogeneous

photocatalysts can both eliminate the contamination of organic products by trace amounts of heavy metals, and also reduce processing and waste disposal costs in large scale reactions.

In recently, porous organic polymers (POPs), such as conjugated microporous polymers (CMPs),<sup>8</sup> polymers of intrinsic microporosity (PIMs),<sup>9</sup> hyper-cross-linked polymers (HCPs),<sup>10</sup> and covalent organic frameworks (COFs),<sup>11</sup> can be constructed from well-designed organic monomers, have attracted significant scientific attention in the area of gas storage/separation,<sup>12</sup> organic photoelectric,<sup>13</sup> and heterogeneous catalysis.<sup>14</sup> In particular, conjugated microporous polymers (CMPs) can serve as an ideal platform for incorporating photosensitive monomers into highly stable, recyclable, and reusable heterogeneous photocatalyst systems by taking advantage of their extended  $\pi$ -conjugation structure and the ability to tune their compositions and properties at the molecular level.<sup>15</sup> For example, Lin *et al.* reported the highly stable and porous cross-linked polymers with phosphorescent [Ru(bpy)<sub>3</sub>]<sup>2+</sup> and [Ir(ppy)<sub>2</sub>(bpy)]<sup>+</sup> building blocks for efficient photocatalysis.<sup>7a</sup> Son *et al.* reported benzodifuran-based CMPs *via* post modification, and the resulting polymer showed high photocatalytic activity for the oxidative conversion of primary amines into imines.<sup>15d</sup> Wang and Zhang *et al.* synthesized conjugated polybenzodiazoles as organic heterogeneous photocatalyst for visible-light-promoted H<sub>2</sub> evolution,<sup>15f</sup> and so on. Remarkable progress has been made in the development of photosensitive monomers based CMPs frameworks for efficient heterogeneous photocatalysis. However, most of these photosensitive monomers either require tedious experimental procedures to prepare or expensive, that limit low-cost preparation of the polymers on a large scale. In this context, the bottom-up construction of

College of Chemistry and Chemical Engineering, Taishan University, Tai'an, Shandong 271021, P. R. China. E-mail: wangcha\_chem@163.com; hanyf1978@163.com

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6ra25123d



heterogeneous photocatalyst directly from the high activity and low cost monomers which without any further synthetic elaboration, may possibly overcome these drawbacks.


Organic dyes have been studied widely in the fields of dye-sensitized solar cells<sup>16</sup> and homogeneous catalysis.<sup>6</sup> Eosin Y (Scheme 1) and Rose Bengal, the most commonly used organic dyes, are demonstrated to be effective noble metal-free photo-organic-catalysts, and have been studied in the area of homogeneous photocatalysis due to their low cost and low toxicity.<sup>6a-d</sup> Eosin Y and Rose Bengal are the ideal candidates to construct photoactive porous organic polymers, the main reasons lie in that: (1) the structural rigidity of the monomers are readily offered by the benzene ring, which could contribute to the construction of rigid POPs frameworks; (2) the bromine or iodine atoms on the benzene ring (without any further synthetic elaboration) could be easily reacted with the structural building blocks; (3) high effective photocatalytic activity, low cost, and low toxicity. Herein, we report the bottom-up construction of robust photoactive porous organic polymers (**EY-POPs**) embedded with Eosin Y dye for highly efficient heterogeneous photocatalytic dehydrogenative coupling

reaction (Scheme 1). Very recently, Jiang and Cooper *et al.* reported conjugated microporous polymers with Rose Bengal dye as heterogeneous organic-photocatalyst for highly efficient aza-Henry reaction.<sup>15c</sup> Unlike the significant work of Jiang and Cooper *et al.*, we synthesized two Eosin Y-functionalized POPs frameworks with different  $\pi$ -conjugation structure, and preliminary investigated the influence of the extended  $\pi$ -conjugation structure on the catalytic activity.

## Results and discussion

### Design, synthesis and characterization of Eosin Y dye-based porous organic polymers (EY-POPs)

One of the key concerns for constructing functional POPs is the rational design of the functional building blocks (FBBs). The desired FBBs candidates should be rigid in structure, suitable in size, easy to prepare, ready to react with the structural building blocks. With these considerations in mind, we accordingly select the skeleton of Eosin Y as the FBB candidate to construct the photoactive porous organic polymers. As illustrated in Scheme 1, the main reasons lie in that: (1) the structural rigidity

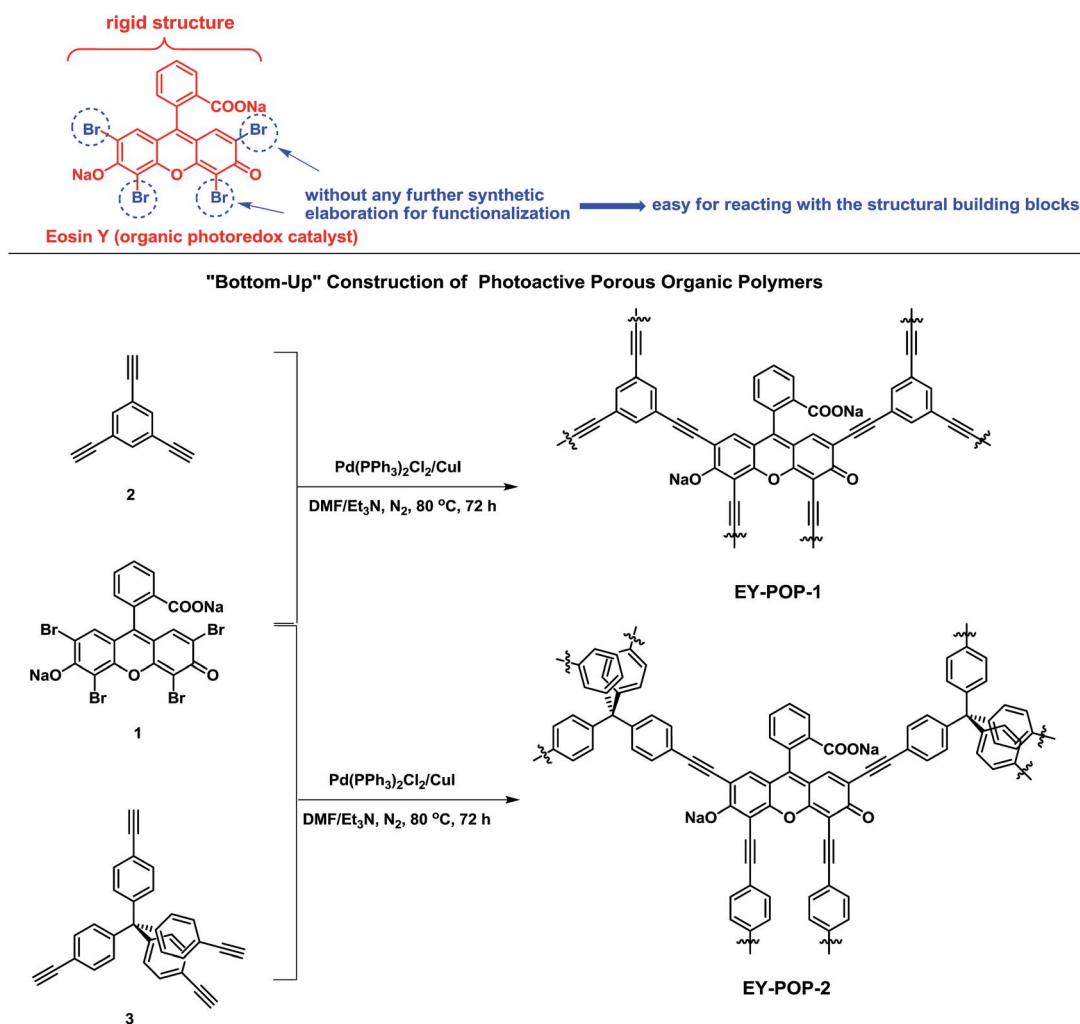

**Scheme 1** Design and synthesis of Eosin Y dye-embedded porous organic polymers (EY-POPs) via the bottom-up strategy.



of organic photoredox catalyst is readily offered by the benzene ring, which could contribute to the construction of rigid POPs frameworks; (2) the bromine atoms on the benzene ring could be easily reacted with the structural building blocks; (3) Eosin Y is demonstrated to be effective noble metal-free photo-organic-catalyst, together with low cost and low toxicity. The polymer networks were easily prepared through palladium-catalyzed Sonogashira–Hagihara cross-coupling reaction of Eosin Y dye (EY) with different structural building blocks (see the Experimental section for experimental details). Reaction of 1,3,5-triethynylbenzene (2) with Eosin Y gave the polymer **EY-POP-1** with extended  $\pi$ -conjugation structure; and the equivalent reaction of tetra(4-ethynylphenyl)methane (3) with Eosin Y gave the copolymer **EY-POP-2** with no extended  $\pi$ -conjugation structure. All the constructed POPs networks are expected to be three-dimensional with varied porosity due to the three-pronged aryleneethynylene linkages and the rigid tetrahedral structure. After the Sonogashira–Hagihara coupling reactions (see Experimental section), the desired Eosin Y-embedded POPs networks were readily precipitated from the solution as red colored solids, both of these polymers are insoluble in all organic solvents tested due to their highly cross-linked structures. The thermogravimetric analysis (TGA) revealed that the **EY-POPs** networks were stable up to 350 °C under a nitrogen atmosphere (Fig. 1a). Power X-ray diffraction measurements indicate that the **EY-POPs** networks are amorphous in nature, as for other reported POPs networks in our laboratory.<sup>17</sup> The UV-visible absorption spectra of **EY-POPs** networks recorded for solid state powders demonstrates that both polymers show broad absorption in the range from 250 to 600 nm (Fig. 1b), which is similar to that of the Eosin Y monomer, indicating that the **EY-POPs** networks can absorb light across a wide range of the visible spectrum.

The absence of the carbon–hydrogen stretching peak of the  $\text{C}\equiv\text{C}$ –H group around  $3280\text{ cm}^{-1}$  in the IR spectra of the **EY-**

**POPs** suggested that most of the alkyne group in the starting materials have been consumed to form  $\text{C}\equiv\text{C}$ – groups in the POPs networks. The high degree of spectral similarity of **EY-POP-1** and **EY-POP-2** also demonstrates the structural consistency of these materials (Fig. 1c). The SEM image of **EY-POPs** displayed rather rough surfaces and the particles were on the order of micrometer in size (Fig. 1d).

The permanent porosity of **EY-POPs** networks were investigated by nitrogen adsorption/desorption measurements at 77 K, and the obtained results are listed in Table S1.† As shown in Fig. 2a and b, both of the **EY-POPs** networks showed similar adsorption and desorption isotherms, and gave rise to type I nitrogen gas sorption isotherms according to the IUPAC classification.<sup>18</sup> The adsorption shows a steep nitrogen gas uptake at low relative pressure, indicating that the materials are microporous. The application of the Brunauer–Emmett–Teller (BET) model resulted in the surface areas of  $587$  and  $718\text{ m}^2\text{ g}^{-1}$  for **EY-POP-1** (Fig. S1, ESI†) and **EY-POP-2** (Fig. S2, ESI†), respectively. As calculated by non-local density functional theory (NLDFT), the pore size distribution (PSD) of **EY-POP-1** and **EY-POP-2** mainly distributed around  $0.7$  and  $1.3\text{ nm}$ , respectively (Fig. 2c and d). This demonstrates a significant proportion of micropores in the **EY-POPs** networks.

The chemical composition of **EY-POPs** networks were characterized by solid-state  $^{13}\text{C}$  cross-polarization magic-angle spinning (CP/MAS) NMR spectroscopy. Fig. 3 shows the  $^{13}\text{C}$  CP/MAS NMR spectra recorded for **EY-POP-1** and **EY-POP-2**. The signals at  $\delta = 168, 156, 147, 129$  and  $102\text{ ppm}$  confirmed that the Eosin Y monomer skeleton has well been embedded into the polymer networks, while the peak at approximately  $82$  and  $93\text{ ppm}$  represent the alkynyl groups in the **EY-POPs** networks. The peak at about  $129$  and  $125\text{ ppm}$  confirm that the 1,3,5-triethynylbenzene skeleton has been successful embedded into the **EY-POP-1** network, and the peak at about  $65, 129$  and  $147\text{ ppm}$  also confirm that the tetra(4-ethynylphenyl)methane skeleton has been successful embedded into the **EY-POP-2**

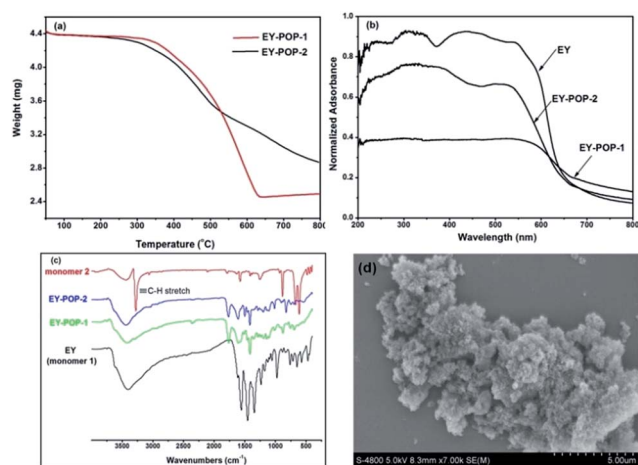


Fig. 1 (a) Thermogravimetric analysis (TGA) curves for **EY-POPs** networks. (b) UV-visible absorption spectra for the monomer of EY and the **EY-POPs** networks as solid state powders. (c) FT-IR comparison of monomer 1 (in black), monomer 2 (in red), **EY-POP-1** (in green), and **EY-POP-2** (in blue). (d) SEM image for the **EY-POP-1** network.

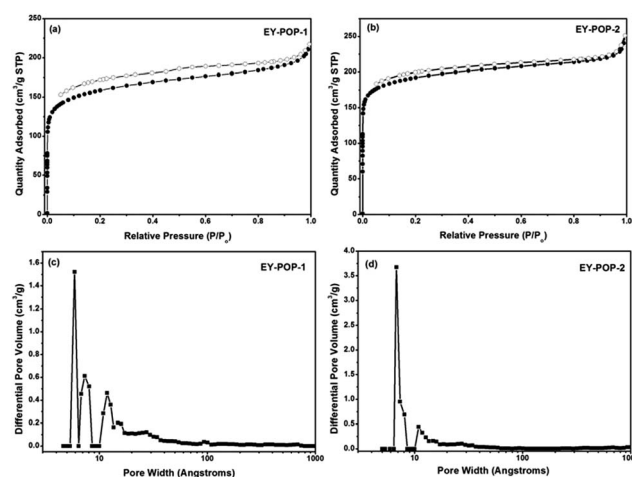


Fig. 2 Nitrogen adsorption/desorption isotherms of **EY-POP-1** (a) and **EY-POP-2** (b). Pore size distribution (PSD) for **EY-POP-1** (c) and **EY-POP-2** (d), calculated with non-local density functional theory (NLDFT).



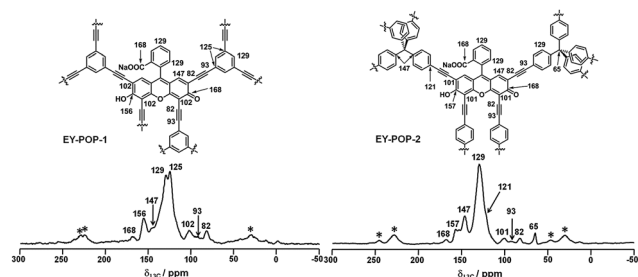


Fig. 3 Solid-state  $^{13}\text{C}$  CP/MAS NMR spectra for EY-POP-1 and EY-POP-2. The assignments for the  $^{13}\text{C}$  MAS NMR signals are indicated (top).

network. All of the results verified the bottom-up construction of the photoactive EY-POPs networks with the Eosin Y skeleton embedded into the frameworks.

### Photocatalytic activity of EY-POPs in the heterogeneous photocatalytic aza-Henry reaction

The dehydrogenative coupling reactions, performed under oxidative conditions, are an important C–C bond formation methodology.<sup>19</sup> Significant progress has been made recently in achieving visible-light-promoted photocatalytic dehydrogenative coupling reactions with transition metal complexes<sup>4</sup> or organic dyes<sup>6b,6d</sup> as the homogeneous photoredox catalysts. However, the practical application of homogeneous photoredox catalysis is generally hindered due to the requirement for high catalyst loadings and the difficulty in separating the catalyst from the product. To address these limitations, heterogenization of the homogeneous catalyst is a promising option. We investigated the aza-Henry reaction of 2-phenyl-1,2,3,4-tetrahydroisoquinoline with nitromethane as a model reaction to estimate the photocatalytic activities of the EY-POPs

networks (Table 1). In an initial experiment, the oxidative coupling of 2-phenyl-1,2,3,4-tetrahydroisoquinoline (0.20 mmol) with nitromethane (1.0 mL) in the presence of EY-POPs (5 mg), visible light (14 W fluorescent lamp) and air was investigated. Both of the EY-POPs polymers (5.0 mg) showed approximately similar photocatalytic activities for this aza-Henry reaction, the reaction proceeded smoothly and gave the desired product in moderate yield after 36 h (Table 1, entries 1 and 2). Strikingly, we found that the reaction proceeded much faster by increasing the catalyst loading of EY-POPs polymers (10 mg), giving the product in high yield after 24 h (Table 1, entries 3 and 4). Amongst the EY-POPs polymers tested, the EY-POP-1 polymer with the extended  $\pi$ -conjugation structure showed the best reactivity, catalysing almost a complete conversion after 24 h with 10 mg catalyst (entry 3). A number of control experiments were carried out to demonstrate the heterogeneous and photocatalytic nature of the reaction. Nature light gave low yield (35%) and there was no reaction in the dark (Table 1, entries 5 and 6), indicating that light is necessary to promote the electron transfer. On the other hand, the background reaction in the absence of EY-POPs polymers but in the presence of light showed only around <5% yield after 36 h (Table 1, entry 7), verifying that the EY-POPs polymers played a catalytic role in the reaction. The effect of oxygen on the reaction was also examined. The reaction proceeded much slower under an  $\text{N}_2$  atmosphere excluding oxygen, giving the product in moderate yield (60%) after 36 h (Table 1, entry 8). For the purpose of comparison, we also investigated the catalytic performance of the homogeneous Eosin Y catalyst under the same reaction condition, it can be seen that the efficiency of EY-POP-1 polymer compares well to that of the homogeneous Eosin Y catalyst (Table 1, entry 9).

The substrate scope of the aza-Henry reaction catalyzed by EY-POP-1 was examined with a variety of tetrahydroisoquinolines and nitromethane/nitroethane (Table 2). As shown in Table 2, good to excellent isolated yields (90–99%) were obtained for all of the aza-Henry reaction of a variety of *N*-aryltetrahydroisoquinolines with nitromethane (Table 2, entries 1–8) and nitroethane (Table 2, entries 9–12) catalyzed by the EY-POP-1 polymer, which are comparable to those using the Ir- or Ru-loaded PCPs,<sup>7a</sup> the RB-CMP network<sup>15c</sup> and the homogeneous organic dye counterpart.<sup>6b,6d</sup> These results identified that the EY-POP-1 nanoporous polymer works as a high efficient heterogeneous organic-photocatalyst for the aza-Henry reaction.

We further investigated the recyclability of EY-POP-1 catalyst in the aza-Henry reaction of 2-(4-chlorophenyl)-1,2,3,4-tetrahydroisoquinoline with nitromethane (Table S2, ESI†). After the reaction, EtOAc was added to dilute the reaction mixture, and the EY-POP-1 catalyst was easily separated from the products by centrifugation and decantation of the reaction solution. The recycled catalyst was further washed with EtOAc to remove residual product, and simple dried in vacuum overnight before reuse. As in Fig. 4, the EY-POP-1 polymer could be reused at least twelve times without any significant loss of the photocatalytic activity (94–98% yield), which is attributed to the built-in character of the covalently linked catalytic sites of EY-POP-1 polymer. However, in the recycling experiments, the reaction

Table 1 Screening condition for the aza-Henry reaction<sup>a</sup>

Entry	Catalyst (× mg)	Light source	Time (h)	Yield <sup>b</sup>
1	EY-POP-1 (5)	14 W bulb	36	65
2	EY-POP-2 (5)	14 W bulb	36	54
3	EY-POP-1 (10)	14 W bulb	24	98
4	EY-POP-2 (10)	14 W bulb	24	87
5	EY-POP-1 (10)	Natural light	36	35
6	EY-POP-1 (10)	Dark	36	Trace
7	—	14 W bulb	36	<5
8 <sup>c</sup>	EY-POP-1 (10)	14 W bulb	36	60
9	Eosin Y (5 mol%)	14 W bulb	24	98


<sup>a</sup> Reaction condition: 2-phenyl-1,2,3,4-tetrahydroisoquinoline (41.8 mg, 0.2 mmol), nitromethane (1.0 mL), and EY-POPs, r.t., 14 W household bulb, in air. <sup>b</sup> Isolated yield after silica gel column chromatography.

<sup>c</sup> The reaction was carried out under  $\text{N}_2$ .






**Table 2** Investigating the substrate scope of the aza-Henry reaction catalyzed by **EY-POP-1**<sup>a</sup>

				
Entry	Substrate	Product	Time (h)	Yield <sup>b</sup> (%)
1			24	98
2			36	94
3			72	91
4			12	98
5			20	99
6			72	99
7			72	97
8			24	94
9			24	94
10			17	90
11			50	91
12			24	92

<sup>a</sup> Reaction conditions: 0.2 mmol substrate; 1.0 mL of nitroalkyl; 10 mg **EY-POP-1**; room temperature; 14 W household bulb; in air. <sup>b</sup> Isolated yield after silica gel column chromatography.

time was prolonged after five cycles, which could be due to the impurities blocking the polymeric nanopores. We found that the BET surface area of **EY-POP-1** from 587 m<sup>2</sup> g<sup>-1</sup> decrease to 347 m<sup>2</sup> g<sup>-1</sup> after the sixth recycle use (Fig. S3†).

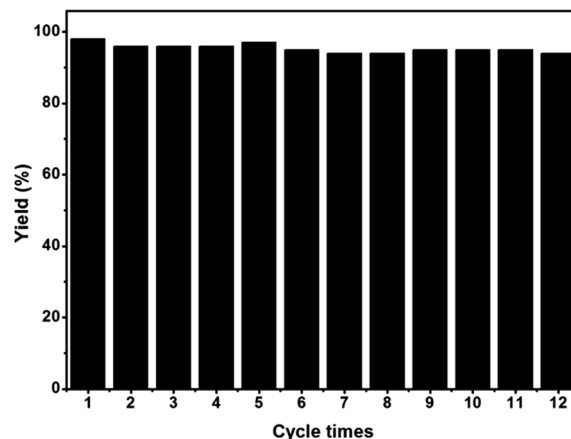**Fig. 4** Recycling experiment of **EY-POP-1** for the aza-Henry reaction of 2-(4-chlorophenyl)-1,2,3,4-tetrahydroisoquinoline and nitromethane.

## Conclusions

In conclusion, the Eosin Y, an organic dye, has been successfully embedded into a nanoporous network **EY-POPs** through a bottom-up strategy. The resultant framework materials are stable in various solvents and are thermally stable. Owing to the high BET surface area and the built-in character of the covalently linked catalytic sites of **EY-POPs**, these photoactive polymers were shown to be highly active, recyclable and reusable heterogeneous photocatalysts in aza-Henry reaction. Catalyzed by the **EY-POP-1** catalyst, the aza-Henry reaction of tetrahydroisoquinolines to nitromethane/nitroethane gives the desired products in good to excellent yield (90–99%). The heterogeneous photocatalyst could be reused at least twelve times without any significant loss of the photocatalytic activity (94–98% yield). This work highlights the potential of using POPs polymers as a stable and molecularly platform for developing heterogeneous photocatalysts for other important organic transformations. Currently, research into the bottom-up construction of chiral porous organic photocatalysts for asymmetric catalysis is underway in our laboratory.

## Experimental section

### Materials

All reagents were purchased from commercial sources. Et<sub>3</sub>N and DMF were dried through the standard procedures. Tetra(4-ethynylphenyl)methane and 1,3,5-triethynylbenzene were prepared according to the literature procedure.<sup>20</sup> Pd(PPh<sub>3</sub>)<sub>2</sub>Cl<sub>2</sub>, PdCl<sub>2</sub> and Eosin Y were purchased from J&K. A range of substrates were synthesized according to the literature procedure.<sup>21</sup> All catalytic reactions were performed in a 15 mL glass tube.

### Synthesis of EY-POP-1

Eosin Y (692 mg, 1.0 mmol), 1,3,5-triethynylbenzene (200 mg, 1.33 mmol), bis-(triphenylphosphine)palladium(II) dichloride (30 mg), and copper(I) iodide (20 mg) were added into a dried round-bottom flask under nitrogen atmosphere. Anhydrous



DMF (10 mL) and Et<sub>3</sub>N (10 mL) were added to the mixture *via* a syringe. The resulting mixture was heated to 80 °C and stirred for 72 h under nitrogen atmosphere. After cooling to room temperature, the precipitate network polymer was filtered and washed four times (once each) with chloroform, water, methanol and acetone to remove any unreacted monomer or catalyst residues. Further purification of the polymer was carried out by Soxhlet extraction with methanol for 48 h. The product was dried at 70 °C under vacuum for 6 h to give a red powder. Yield: 465 mg (82%). Anal. calcd for C<sub>36</sub>H<sub>10</sub>Na<sub>2</sub>O<sub>5</sub>: C, 76.06; H, 1.76. Found: C, 62.38, H, 1.25.

### Synthesis of EY-POP-2

Eosin Y (296 mg, 0.43 mmol), tetra(4-ethynylphenyl)methane (178 mg, 0.43 mmol), bis-(triphenylphosphine)palladium(II) dichloride (15 mg), and copper(I) iodide (10 mg) were added into a dried round-bottom flask under nitrogen atmosphere. Anhydrous DMF (5.0 mL) and Et<sub>3</sub>N (5.0 mL) were added to the mixture *via* a syringe. The resulting mixture was heated to 80 °C and stirred for 72 h under nitrogen atmosphere. After cooling to room temperature, the precipitate network polymer was filtered and washed four times (once each) with chloroform, water, methanol and acetone to remove any unreacted monomer or catalyst residues. Further purification of the polymer was carried out by Soxhlet extraction with methanol for 48 h. The product was dried at 70 °C under vacuum for 6 h to give a red powder. Yield: 299 mg (89%). Anal. calcd for C<sub>53</sub>H<sub>22</sub>Na<sub>2</sub>O<sub>5</sub>: C, 81.12; H, 2.81. Found: C, 69.94, H, 2.20.

### General procedure for the aza-Henry reaction catalyzed by EY-POP-1

In a typical run of catalytic activity test of **EY-POP-1**, *N*-aryltetrahydroisoquinolines (0.2 mmol), nitroalkane (1.0 mL), and **EY-POP-1** (10 mg) were added into a 15 mL glass tube. The tube was sealed with a rubber stopper and the reaction mixture was connected to the air through a needle in the stopper. The tube was subsequently stirred at room temperature under irradiation with visible light using a cool daylight energy-saving bulb (14 W) until all starting material had been consumed. After the reaction was completed (monitored by TLC), the mixture was centrifuged and the solid was washed with EtOAc (3 × 5 mL). The combined organic phase was then concentrated and purified by flash column chromatography with petroleum ether/EtOAc = 10 : 1 as the eluent to give the pure product.

### Typical recycling procedure for the aza-Henry reaction catalyzed by EY-POP-1

The recycling experiment was performed by recovering the **EY-POP-1** catalyst using the centrifugation method. The recovered **EY-POP-1** catalyst was washed with EtOAc to remove the residual product and simply dried before reuse. We chose the aza-Henry reaction of 2-(4-chlorophenyl)-1,2,3,4-tetrahydroisoquinoline to nitromethane to investigate the recyclability of **EY-POP-1** catalyst, and the results are summarized in Table S2.†

### Physical characterization

Thin-layer chromatography (TLC) plates were visualized by exposure to ultraviolet light. Flash column chromatography (FCC) was carried out with silica gel (200–300 mesh). <sup>1</sup>H and <sup>13</sup>C liquid NMR spectra were recorded on a Bruker Avance III 400 MHz NMR spectrometer. The chemical shifts  $\delta$  are given in ppm (parts per million) relative to tetramethylsilane (TMS) and the coupling constants *J* are given in Hz. All the spectra were recorded in CDCl<sub>3</sub> as solvent at room temperature. TMS served as the internal standard ( $\delta$  = 0.00 ppm) for <sup>1</sup>H NMR, while CDCl<sub>3</sub> as the internal standard ( $\delta$  = 77.0 ppm) for <sup>13</sup>C NMR. FT-IR spectra were recorded on a Nicolet NEXUS 670 instrument. N<sub>2</sub> adsorption and desorption isotherms were measured at 77 K using a Micromeritics ASAP 2020M system. The pore-size-distribution curves were obtained from the adsorption branches using non-local density functional theory (NLDFT) method. Solid-state NMR experiments were performed on a Bruker Avance II WB 400 MHz NMR spectrometer. The <sup>13</sup>C CP/MAS NMR spectra were recorded with the contact time of 3 ms (ramp 100) and the recycle delay of 2 s on a 2.5 mm double resonance probe. The thermal properties of the polymer networks were evaluated using a thermogravimetric analysis (TGA)-differential thermal analysis instrument (METTLER, TGA/DSC 1/1100) over the temperature range 25 to 800 °C under nitrogen atmosphere with a heating rate of 10 °C min<sup>-1</sup>. Powder X-ray diffraction (PXRD) data were collected with a Rigaku D/MAX-2400 X-ray diffractometer operated at 40 kV and 100 mA with Cu K $\alpha$  radiation at a scan rate of 15° min<sup>-1</sup>. Field emission scanning electron microscopy (SEM) observations were performed on Hitachi S-4800 microscope operated at an accelerating voltage of 5.0 kV. The UV-visible absorption spectra of the Eosin Y monomer and the **EY-POPs** networks were recorded on UV-Vis spectrometer (U-4100) in solid state powder at room temperature. Elemental analysis was performed on an Elementar Analysensysteme GmbH VarioEL V3.00 elemental analyzer.

### Acknowledgements

This work was supported by the National Natural Science Foundation of China (No. 21502136, 21571137), Higher Educational Science and Technology Program of Shandong Province (No. J15LC18), and the Promotive Research Fund for Excellent Young and Middle-aged Scientists of Shandong Province (No. BS2014CL035).

### Notes and references

- (a) M. Fagnoni, D. Dondi, D. Ravelli and A. Albin, *Chem. Rev.*, 2007, **107**, 2725–2756; (b) T. P. Yoon, M. A. Ischay and J. Du, *Nat. Chem.*, 2010, **2**, 527–532; (c) J. M. R. Narayanam and C. R. J. Stephenson, *Chem. Soc. Rev.*, 2011, **40**, 102–113; (d) J. Xuan and W.-J. Xiao, *Angew. Chem., Int. Ed.*, 2012, **51**, 6828–6838.
- C. K. Prier, D. A. Rankic and D. W. C. MacMillan, *Chem. Rev.*, 2013, **113**, 5322–5363.
- (a) R. S. Andrews, J. J. Becker and M. R. Gagné, *Angew. Chem., Int. Ed.*, 2010, **49**, 7274–7276; (b) J. D. Nguyen, J. W. Tucker,



- M. D. Konieczynska and C. R. J. Stephenson, *J. Am. Chem. Soc.*, 2011, **133**, 4160–4163; (c) T. Maji, A. Karmakar and O. Reiser, *J. Org. Chem.*, 2011, **76**, 736–739; (d) J. Du, L. R. Espelt, I. A. Guzei and T. P. Yoon, *Chem. Sci.*, 2011, **2**, 2115–2119.
- 4 A. G. Condie, J. C. González-Gómez and C. R. J. Stephenson, *J. Am. Chem. Soc.*, 2010, **132**, 1464–1465.
- 5 D. A. Nicewicz and D. W. MacMillan, *Science*, 2008, **322**, 77–80.
- 6 (a) H. Liu, W. Feng, C. W. Kee, Y. Zhao, D. Leow, Y. Pan and C.-H. Tan, *Green Chem.*, 2010, **12**, 953–956; (b) D. P. Hari and B. König, *Org. Lett.*, 2011, **13**, 3852–3855; (c) M. Neumann, S. Földner, B. König and K. Zeitler, *Angew. Chem., Int. Ed.*, 2011, **50**, 951–954; (d) Y. Pan, C. W. Kee, L. Chen and C.-H. Tan, *Green Chem.*, 2011, **13**, 2682–2685; (e) Y. Pan, S. Wang, C. W. Kee, E. Dubuisson, Y. Yang, K. P. Loh and C.-H. Tan, *Green Chem.*, 2011, **13**, 3341–3344; (f) K. Ohkubo, K. Mizushima, R. Iwata and S. Fukuzumi, *Chem. Sci.*, 2011, **2**, 715–722; (g) D. Ravelli and M. Fagnoni, *ChemCatChem*, 2012, **4**, 169–171; (h) D. Ravelli, M. Fagnoni and A. Albini, *Chem. Soc. Rev.*, 2013, **42**, 97–113.
- 7 (a) Z. Xie, C. Wang, K. E. deKrafft and W. Lin, *J. Am. Chem. Soc.*, 2011, **133**, 2056–2059; (b) P. Wu, C. He, J. Wang, X. Peng, X. Li, Y. An and C. Duan, *J. Am. Chem. Soc.*, 2012, **134**, 14991–14999; (c) M. Liras, M. Iglesias and F. Sánchez, *Macromolecules*, 2016, **49**, 1666–1673.
- 8 (a) J.-X. Jiang, F. Su, A. Trewin, C. D. Wood, N. L. Campbell, H. Niu, C. Dickinson, A. Y. Ganin, M. J. Rosseinsky, Y. Z. Khimyak and A. I. Cooper, *Angew. Chem., Int. Ed.*, 2007, **46**, 8574–8578; (b) J.-X. Jiang, F. Su, A. Trewin, C. D. Wood, H. Niu, J. T. A. Jones, Y. Z. Khimyak and A. I. Cooper, *J. Am. Chem. Soc.*, 2008, **130**, 7710–7720; (c) A. I. Cooper, *Adv. Mater.*, 2009, **21**, 1291–1295.
- 9 (a) N. B. McKeown and P. M. Budd, *Chem. Soc. Rev.*, 2006, **35**, 675–683; (b) M. Hashem, C. Grazia Bezzu, B. M. Kariuki and N. B. McKeown, *Polym. Chem.*, 2011, **2**, 2190–2192; (c) J. Vile, M. Carta, C. G. Bezzu and N. B. McKeown, *Polym. Chem.*, 2011, **2**, 2257–2260; (d) P. Zhang, X. Jiang, S. Wan and S. Dai, *J. Mater. Chem. A*, 2015, **3**, 6739–6741; (e) E. Madrid, P. Cottis, Y. Rong, A. T. Rogers, J. M. Stone, R. Malpass-Evans, M. Carta, N. B. McKeown and F. Marken, *J. Mater. Chem. A*, 2015, **3**, 15849–15853; (f) S. Yi, X. Ma, I. Pinnau and W. J. Koros, *J. Mater. Chem. A*, 2015, **3**, 22794–22806.
- 10 M. P. Tsyurupa and V. A. Davankov, *React. Funct. Polym.*, 2006, **66**, 768–779.
- 11 (a) X. Feng, X. Ding and D. Jiang, *Chem. Soc. Rev.*, 2012, **41**, 6010–6022; (b) S.-Y. Ding and W. Wang, *Chem. Soc. Rev.*, 2013, **42**, 548–568; (c) P. J. Waller, F. Gándara and O. M. Yaghi, *Acc. Chem. Res.*, 2015, **48**, 3053–3063.
- 12 (a) T. Ben, H. Ren, S. Ma, D. Cao, J. Lan, X. Jing, W. Wang, J. Xu, F. Deng, J. M. Simmons, S. Qiu and G. Zhu, *Angew. Chem., Int. Ed.*, 2009, **48**, 9457–9460; (b) S. Yuan, S. Kirklin, B. Dorney, D.-J. Liu and L. Yu, *Macromolecules*, 2009, **42**, 1554–1559; (c) E. Klontzas, E. Tylanakis and G. E. Froudakis, *Nano Lett.*, 2010, **10**, 452–454; (d) A. Li, R.-F. Lu, Y. Wang, X. Wang, K.-L. Han and W.-Q. Deng, *Angew. Chem., Int. Ed.*, 2010, **49**, 3330–3333; (e) Q. Chen, M. Luo, P. Hammershøj, D. Zhou, Y. Han, B. W. Laursen, C.-G. Yan and B.-H. Han, *J. Am. Chem. Soc.*, 2012, **134**, 6084–6087.
- 13 (a) J. Weber and A. Thomas, *J. Am. Chem. Soc.*, 2008, **130**, 6334–6335; (b) L. Chen, Y. Honsho, S. Seki and D. Jiang, *J. Am. Chem. Soc.*, 2010, **132**, 6742–6748; (c) Y. Xu, L. Chen, Z. Guo, A. Nagai and D. Jiang, *J. Am. Chem. Soc.*, 2011, **133**, 17622–17625.
- 14 (a) P. Kaur, J. T. Hupp and S. T. Nguyen, *ACS Catal.*, 2011, **1**, 819–835; (b) Y. Zhang and S. N. Riduan, *Chem. Soc. Rev.*, 2012, **41**, 2083–2094; (c) M. Rose, *ChemCatChem*, 2014, **6**, 1166–1182; (d) C.-A. Wang and W. Wang, *Acta Chim. Sin.*, 2015, **73**, 498–529.
- 15 (a) M. G. Schwab, M. Hamburger, X. Feng, J. Shu, H. W. Spiess, X. Wang, M. Antonietti and K. Mullen, *Chem. Commun.*, 2010, **46**, 8932–8934; (b) K. Zhang, D. Kopetzki, P. H. Seeberger, M. Antonietti and F. Vilela, *Angew. Chem., Int. Ed.*, 2013, **52**, 1432–1436; (c) J.-X. Jiang, Y. Li, X. Wu, J. Xiao, D. J. Adams and A. I. Cooper, *Macromolecules*, 2013, **46**, 8779–8783; (d) N. Kang, J. H. Park, K. C. Ko, J. Chun, E. Kim, H.-W. Shin, S. M. Lee, H. J. Kim, T. K. Ahn, J. Y. Lee and S. U. Son, *Angew. Chem., Int. Ed.*, 2013, **52**, 6228–6232; (e) Z. J. Wang, K. Garth, S. Ghasimi, K. Landfester and K. A. I. Zhang, *ChemSusChem*, 2015, **8**, 3459–3464; (f) R. S. Sprick, J.-X. Jiang, B. Bonillo, S. Ren, T. Ratvijitvech, P. Guiglion, M. A. Zwijnenburg, D. J. Adams and A. I. Cooper, *J. Am. Chem. Soc.*, 2015, **137**, 3265–3270; (g) W. Liang, T. L. Church, S. Zheng, C. Zhou, B. S. Haynes and D. M. D'Alessandro, *Chem.-Eur. J.*, 2015, **21**, 18576–18579; (h) L. Pan, M.-Y. Xu, L.-J. Feng, Q. Chen, Y.-J. He and B.-H. Han, *Polym. Chem.*, 2016, **7**, 2299–2307; (i) C. Yang, B. C. Ma, L. Zhang, S. Lin, S. Ghasimi, K. Landfester, K. A. I. Zhang and X. Wang, *Angew. Chem., Int. Ed.*, 2016, **55**, 9202–9206; (j) L. Li, Z. Cai, Q. Wu, W.-Y. Lo, N. Zhang, L. X. Chen and L. Yu, *J. Am. Chem. Soc.*, 2016, **138**, 7681–7686; (k) R. S. Sprick, B. Bonillo, R. Clowes, P. Guiglion, N. J. Brownbill, B. J. Slater, F. Blanc, M. A. Zwijnenburg, D. J. Adams and A. I. Cooper, *Angew. Chem., Int. Ed.*, 2016, **55**, 1792–1796.
- 16 A. Mishra, M. K. R. Fischer and P. Bäuerle, *Angew. Chem., Int. Ed.*, 2009, **48**, 2474–2499.
- 17 (a) C. A. Wang, Z. K. Zhang, T. Yue, Y. L. Sun, L. Wang, W. D. Wang, Y. Zhang, C. Liu and W. Wang, *Chem.-Eur. J.*, 2012, **18**, 6718–6723; (b) C.-A. Wang, Y.-F. Han, Y.-W. Li, K. Nie, X.-L. Cheng and J.-P. Zhang, *RSC Adv.*, 2016, **6**, 34866–34871; (c) C.-A. Wang, Y.-W. Li, X.-M. Hou, Y.-F. Han, K. Nie and J.-P. Zhang, *ChemistrySelect*, 2016, **1**, 1371–1376.
- 18 K. S. W. Sing, D. H. Everett, R. A. W. Haul, L. Moscou, R. A. Prccrotti, J. Rouquerol and T. Siemieniowska, *Pure Appl. Chem.*, 1985, **57**, 603–619.
- 19 C.-J. Li, *Acc. Chem. Res.*, 2009, **42**, 335–344.
- 20 (a) T. Kuroda, Y. Sakurai, Y. Suzuki, A. O. Nakamura, M. Kuwahara, H. Ozaki and H. Sawai, *Chem.-Asina J.*, 2006, **1**, 575–580; (b) S. Yuan, S. Kirklin, B. Dorney, J.-J. Liu and L. Yu, *Macromolecules*, 2009, **42**, 1554–1559.
- 21 F. Y. Kwong, A. Klapars and S. L. Buchwald, *Org. Lett.*, 2002, **4**, 581–584.

