



Cite this: *Chem. Sci.*, 2021, **12**, 5843

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 9th December 2020
Accepted 15th March 2021

DOI: 10.1039/d0sc06734b
rsc.li/chemical-science

Non-concentrated aqueous electrolytes with organic solvent additives for stable zinc batteries†‡

Yang Dong,§^a Licheng Miao,§^{bc} Guoqiang Ma,^a Shengli Di,^a Yuanyuan Wang,^a Liubin Wang,^{ab} Jianzhong Xu^a and Ning Zhang  ^{ab}*

Rechargeable aqueous zinc batteries (RAZBs) are promising for large-scale energy storage because of their superiority in addressing cost and safety concerns. However, their practical realization is hampered by issues including dendrite growth, poor reversibility and low coulombic efficiency (CE) of Zn anodes due to parasitic reactions. Here, we report a non-concentrated aqueous electrolyte composed of 2 m zinc trifluoromethanesulfonate ($Zn(OTf)_2$) and the organic dimethyl carbonate (DMC) additive to stabilize the Zn electrochemistry. Unlike the case in conventional aqueous electrolytes featuring typical $Zn[H_2O]_6^{2+}$ solvation, a solvation sheath of Zn^{2+} with the co-participation of the DMC solvent and OTf^- anion is found in the formulated $H_2O + DMC$ electrolyte, which contributes to the formation of a robust ZnF_2 and $ZnCO_3$ -rich interphase on Zn. The resultant Zn anode exhibits a high average CE of Zn plating/stripping (99.8% at an areal capacity of 2.5 mA h cm^{-2}) and dendrite-free cycling over 1000 cycles. Furthermore, the $H_2O + DMC$ electrolytes sustain stable operation of RAZBs pairing Zn anodes with diverse cathode materials such as vanadium pentoxide, manganese dioxide, and zinc hexacyanoferrate. Rational electrolyte design with organic solvent additives would promote building better aqueous batteries.

Introduction

Safe, reliable, and cost-effective electrochemical energy storage technologies are demanded for the efficient utilization of renewable energy sources such as solar and wind.^{1,2} Among various options, rechargeable aqueous Zn batteries (RAZBs) hold great promise because of the advantages of metallic Zn anodes including abundant resources, environmental benignancy, low cost, and high theoretical specific/volumetric capacity (820 mA h g^{-1} and 5855 mA h cm^{-3}).^{3–5} Moreover, compared with flammable organic electrolytes widely adopted in lithium-ion batteries (LIBs), aqueous electrolytes intrinsically provide improved safety, and their higher ionic conductivities favor high rate capability.^{6,7} These features promote the recent renaissance of RAZBs with extensive research on a variety of cathode materials, including manganese oxides,^{8–10} Prussian blue analogues,^{11,12} vanadium oxides,^{13–16} and organic compounds.^{17–20}

Nonetheless, state-of-the-art RAZBs are plagued by the issues associated with metallic Zn anodes, such as low plating/stripping efficiency, dendrite growth, and unstable Zn-electrolyte interface along with water-induced side reactions (e.g., H_2 evolution and surface passivation).^{4,21,22} To address these challenges, an efficient strategy is to construct hierarchical structures^{23–26} or modification layers^{27–30} on Zn anodes. Besides, electrolyte modulation is considered to be a facile approach to stabilize metal anodes by regulating the interface chemistry.^{31–35} Recently, highly concentrated electrolytes (e.g., 1 m $Zn(TFSI)_2 + 20\text{ m LiTFSI}$ (m: mol kg^{-1}))³⁶ and deep eutectic electrolytes (e.g., $\sim 4.2\text{ m Zn(TFSI)}_2$ in nonaqueous acetamide³⁷) were proposed to form an anion-derived solid electrolyte interphase (SEI) layer on the Zn anode. This SEI allows rapid Zn^{2+} diffusion while blocking solvents and electrons, and thus suppressing water-induced side reactions.^{36,37} However, the higher cost, reduced ionic conductivity, and increased viscosity of these salt-concentrated electrolytes raise much concern towards their practical use. In a conventional aqueous electrolyte (concentration generally below 2 mol L^{-1}), the typical solvation structure of $Zn[H_2O]_6^{2+}$ without anion coordination makes it infeasible to form a protective SEI from the reductive decomposition of anions before Zn deposition.^{35,36} Instead, competitive water decomposition with H_2 evolution occurred ($H_2O \rightarrow H_2 + OH^-$), which increases the local pH and induces the generation of Zn hydroxides or zincates to passivate the Zn anode.^{35,38} Therefore, it is desirable to stabilize the Zn electrochemistry in non-concentrated aqueous electrolytes.

^aCollege of Chemistry & Environmental Science, Key Laboratory of Analytical Science and Technology of Hebei Province, Hebei University, Baoding, 071002, China.
E-mail: ningzhang@hbu.edu.cn

^bKey Laboratory of Advanced Energy Materials Chemistry (Ministry of Education), College of Chemistry, Nankai University, Tianjin, 300071, China

^cCollege of Physics and Optoelectronic Engineering, Shenzhen University, Shenzhen, 518060, China

† Dedicated to the 100th anniversary of Hebei University.

‡ Electronic supplementary information (ESI) available. See DOI: 10.1039/d0sc06734b

§ These authors contributed equally to this work.



Herein, an aqueous electrolyte composed of 2 m Zn(CF_3SO_3)₂ (Zn(OTf)₂) in water with the dimethyl carbonate (DMC) additive is developed and demonstrated to form a stable SEI layer on the Zn anode. Based on molecular dynamics (MD) simulations, density functional theory (DFT) computations and spectroscopic investigations (*i.e.*, FTIR, ^{17}O NMR, and Raman), a new solvation shell of Zn²⁺ with the co-participation of the DMC solvent and OTf⁻ anion is found in the formulated H₂O + DMC electrolyte. The co-solvation process enables the formation of an organic-inorganic hybrid SEI with rich ZnF₂ and ZnCO₃, which is proposed to derive from the reductive decomposition of Zn²⁺-DMC and Zn²⁺-OTf⁻ coordinations before Zn deposition. This hybrid SEI effectively suppresses water-induced parasitic reactions on the Zn anode, and thus enables high-efficiency Zn plating/stripping and extended dendrite-free cycling. In addition, the Zn(OTf)₂ in the H₂O + DMC electrolyte is versatilely compatible with different cathode materials such as transition metal oxides and hexacyanoferrate.

Results and discussion

Electrolyte formulation and characterization

Dimethyl carbonate (DMC) as a primary co-solvent has been widely used in LIBs, and its favorable reduction results in the formation of the SEI on the anode surface, which can stabilize the electrode/electrolyte interface and support cation transfer.³⁹ Inspired by this co-solvent design, we have constructed aqueous electrolytes with the DMC additive for RAZBs by mixing water and DMC in varied molar ratios and then adding Zn(OTf)₂ salt into the mixed solvent with a constant concentration of 2 m (m: mol kg⁻¹, Fig. S1, ESI[‡]). The molar ratios between water and DMC solvents are tentatively selected at 8 : 1, 6 : 1, 4 : 1, and 2 : 1, and the corresponding electrolytes are denoted as W8D1, W6D1, W4D1, and W2D1, respectively. A 2 m Zn(OTf)₂ aqueous electrolyte without DMC (denoted as 2 m W) was also prepared for comparison. The compositions of these electrolytes are summarized in Table S1 (ESI[‡]). As a non-polar solvent, DMC is immiscible with polar water (Fig. 1a) and it is not readily soluble with Zn(OTf)₂ salt (Fig. S2, ESI[‡]). Interestingly, the miscibility between DMC and water can be regulated (Fig. 1b) by adding Zn(OTf)₂ salt, which acts as a linker interplaying with both DMC and H₂O (discussed later). Molecular dynamics (MD) simulations reveal the homogeneous solution state (Fig. 1c) of 2 m Zn(OTf)₂ in the H₂O + DMC electrolyte and the apparent phase separation (Fig. 1d) of the H₂O + DMC mixture without salt. Ignition tests intuitively identify the non-flammable nature of W4D1 and W8D1 electrolytes (Fig. 1e and S3, ESI[‡]), whereas, further increasing the DMC content in the electrolyte (*e.g.*, W2D1) leads to electrolyte combustion (Fig. 1f). Although the ionic conductivity of Zn(OTf)₂ in H₂O + DMC electrolytes gradually decreases with increasing DMC ratio, a considerable conductivity of 25.4 mS cm⁻¹ is obtained in W4D1 (Fig. S4, ESI[‡]). This value is much higher than those of typical non-aqueous electrolytes (1–10 mS cm⁻¹).^{1,39}

The solvation structure of H₂O + DMC electrolytes and the interaction between Zn(OTf)₂ and the solvent were investigated by different spectroscopic methods. Fig. 1g presents the Fourier

transform infrared (FTIR) spectra of H₂O + DMC electrolytes along with the neat DMC and H₂O solvents. The broad O-H stretching band can be ascribed to three states of water molecules using the Gaussian function:⁴⁰ (1) “network water (NW)” (\sim 3205 cm⁻¹) associated with water molecules with a strong H-bond coordination (coordination number close to four); (2) “intermediate water (IW)” (\sim 3410 cm⁻¹) corresponding to water molecules with distorted H-bonds and somewhat connected to other water molecules though unable to build a fully connected network; (3) “multimer water (MW)” (\sim 3560 cm⁻¹) ascribed to water molecules standing as free monomers or dimers or trimers and being poorly connected to their environment. Accordingly, the addition of DMC significantly disrupts the strong H-bonding network as confirmed by the significant decrease of the “network water” fraction from 52.9% in pristine 2 m W to 27.5% in W2D1 (Fig. S5, ESI[‡]). Nuclear magnetic resonance (NMR) spectra demonstrate that the ^{17}O chemical shift in H₂O (0 ppm) experiences a downshift (high field) accompanied by peak broadening upon the addition of DMC (Fig. 1h). This evolution reveals that the increase of electron density on oxygen (water) caused by the breaking of the H-bond network results in the shielding effect.^{41,42} The ^{17}O chemical shift of DMC solvent is provided in Fig. S6 (ESI[‡]).

Raman spectra of the H₂O + DMC series also unveil the evolution of the solvation configuration. As shown in Fig. 1i, pure DMC shows a broad peak at \sim 916 cm⁻¹, which is associated with the CH₃-O stretching mode of the free DMC.^{43,44} With the addition of DMC into aqueous electrolytes, a new band located at \sim 923 cm⁻¹ appears owing to the coordination of DMC with Zn²⁺. Note that Lewis acidic Zn²⁺ can interact with the lone-pair of electrons on O from DMC (Lewis base), making the DMC-Zn²⁺ coordination feasible. Moreover, the calculated binding energy of the DMC-Zn²⁺ complex is lower than that of the H₂O-Zn²⁺ counterpart (Fig. S7, ESI[‡]), indicating that DMC can favourably coordinate with Zn²⁺. The fitting results demonstrate that the contents of DMC bound to Zn²⁺ in the electrolyte samples (Table S1, ESI[‡]) gradually increase with the addition of DMC (from W8D1 to W2D1, Table S3, ESI[‡]). Further increasing the DMC ratio (from W4D1 to W2D1) leads to the increase of the free DMC fraction, which could explain the flammable nature of the W2D1 electrolyte (Fig. 1e). In the Raman region of the OTf⁻ anion (Fig. 1j), three broad peaks at \sim 1028, 1032, and 1037 cm⁻¹ represent the free anion (FA), solvent-separated ion pairs (SSIP, Zn²⁺-(H₂O)_x(DMC)_y-OTf⁻) and contact ion pairs (CIP, Zn²⁺-OTf⁻), respectively.⁴⁵ Similar to previous reports,^{36,37} the majority of OTf⁻ anions do not directly connect with Zn²⁺ in the non-concentrated 2 m W electrolyte. Upon adding DMC into aqueous electrolytes, the portion of the Zn²⁺-OTf⁻ coordination significantly strengthens in W4D1 as compared to that in 2 m W (Table S4, ESI[‡]), suggesting the involvement of the OTf⁻ anion in the Zn²⁺ solvation sheath. Additionally, the SSIP signal experiences a slight redshift with the addition of DMC (from W8D1 to W2D1), indicating that the reduced coulombic interaction may be due to the barriers of DMC.

MD simulations were performed to study the Zn²⁺-solvation sheath in 2 m W and H₂O + DMC (W4D1) electrolytes. The



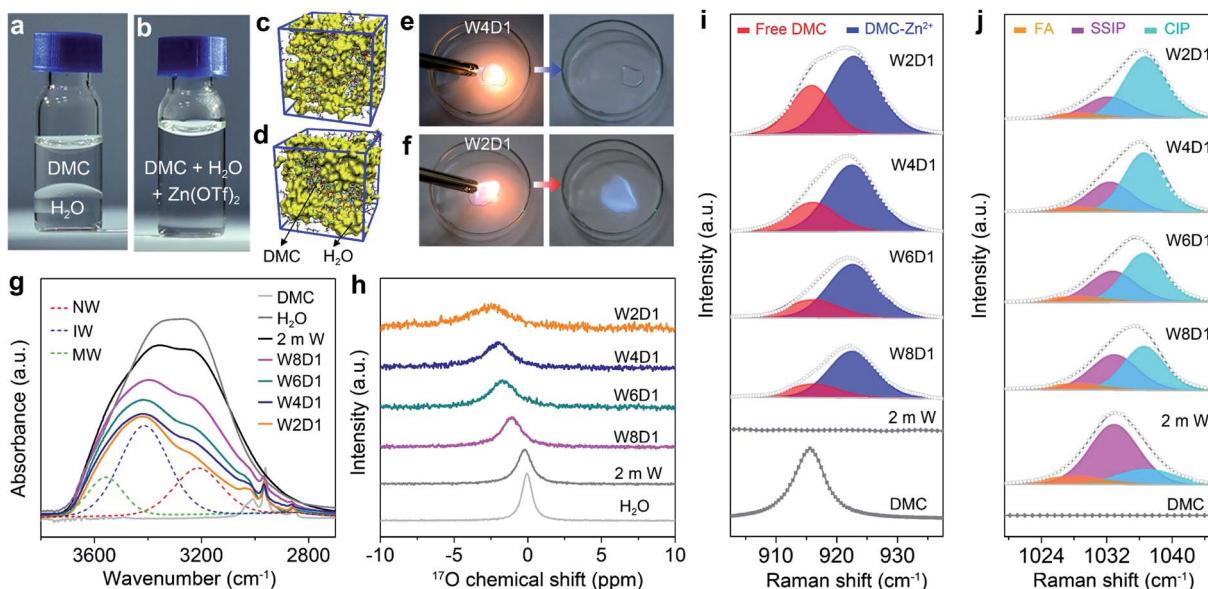


Fig. 1 Electrolyte characterization. Digital photos of (a) the immiscibility between H_2O and DMC solvents, and (b) the homogeneous 2 m $\text{Zn}(\text{OTf})_2$ in a $\text{H}_2\text{O} + \text{DMC}$ electrolyte (W4D1). 3D snapshots obtained from MD simulations showing (c) the miscibility of the W4D1 electrolyte and (d) the phase separation of H_2O and DMC solvents (H_2O domain in yellow and DMC as the wireframe). Ignition tests of (e) W4D1 and (f) W2D1. (g) FTIR spectra of 2 m W, W8D1, W6D1, W4D1 and W2D1 electrolytes, and typical fitted curves (dashed line) of W2D1. (h) Chemical shifts of ^{17}O nuclei of H_2O in $\text{H}_2\text{O} + \text{DMC}$ electrolytes. Raman spectra between (i) 903 and 937 cm^{-1} ($\text{CH}_3\text{–O}$ stretching vibration of DMC) and (j) 1019 and 1045 cm^{-1} (SO_3 stretching mode) of different $\text{H}_2\text{O} + \text{DMC}$ electrolytes.

particular number of ions and molecules in the simulation box is summarized in Table S2 (ESI[‡]). In the non-concentrated aqueous electrolyte (2 m W), Zn^{2+} is considered to coordinate with six H_2O molecules ($\text{Zn}[\text{H}_2\text{O}]_6^{2+}$) without considerable contribution from OTf^- anions. In W4D1, the DMC solvent and OTf^- anion occur in the Zn^{2+} -solvation structure (schematically shown in Fig. 2a), due to the strong interaction among Zn^{2+} , OTf^- and DMC, and the decreased ratio of water. This evolution of the Zn^{2+} structure agrees with the spectroscopic results. Radial distribution functions (RDFs) revealing the distributions of nearest-neighbor molecules¹⁹ were further employed to elucidate the solvation information of W4D1 (Fig. 2b). RDFs show that the primary solvation shell of Zn^{2+} (central ion) is around 0.4 nm in distance. Two peaks of the Zn–O (DMC) pair and Zn–O (OTf^-) pair are identified at 0.33 and 0.37 nm, respectively, supporting the participation of DMC and OTf^- in the Zn^{2+} -solvation structure. In W4D1, the first Zn^{2+} -solvation sheath is occupied primarily by 3.9 H_2O molecules, 0.7 DMC solvent, and 1.4 OTf^- anions on average (*i.e.*, $\text{Zn}^{2+}[\text{H}_2\text{O}]_{3.9}[\text{DMC}]_{0.7}[\text{OTf}^-]_{1.4}$). The RDFs in W8D1 are provided in Fig. S8 (ESI[‡]). Furthermore, the fraction of free water is $\sim 82\%$ in 2 m W and decreases to $\sim 55\%$ in the W4D1 electrolyte (Fig. 2c). This decrease suggests significantly reduced water activity, which favors the suppression of parasitical Zn–water reactions. In addition, the predicted ionic conductivities of the electrolytes are in good agreement with the experimental values (Fig. S4, ESI[‡]), demonstrating the validity of MD simulations.

According to the combination of experimental (FTIR, ^{17}O -NMR, and Raman spectra) and modeling investigations, we propose that the significant interaction among Zn^{2+} , OTf^- , and

DMC provides a unique Zn^{2+} -solvation structure in the W4D1 electrolyte with the co-participation of the DMC solvent and OTf^- anion to form $\text{Zn}^{2+}[\text{H}_2\text{O}]_{3.9}[\text{DMC}]_{0.7}[\text{OTf}^-]_{1.4}$. This solvation structure differs from that of the typical solvation shell (*i.e.*, $\text{Zn}[\text{H}_2\text{O}]_6^{2+}$) in a non-concentrated aqueous electrolyte without DMC solvent. The co-contribution of anion OTf^- and DMC further enables a new interface chemistry induced by the reductive decomposition of OTf^- and DMC and stabilizes Zn electrochemistry, as discussed below.

Reversibility and stability of the Zn anode in $\text{H}_2\text{O} + \text{DMC}$ electrolytes

The Zn plating/stripping properties in $\text{H}_2\text{O} + \text{DMC}$ electrolytes were evaluated using Zn/Ti asymmetric cells and Zn/Zn symmetric cells. Fig. 3a shows the CE of Zn plating/stripping in Zn/Ti cells recorded at a current density of 1.0 mA cm^{-2} , a deposition capacity of 1.0 mA h cm^{-2} and a cut-off voltage of 0.5 V (vs. Zn^{2+}/Zn). The CE value is defined as the ratio of the stripping capacity to the plating capacity. Clearly, the reversibility and stability of the Zn anode improve with increasing DMC content. The Zn/Ti cell in the W4D1 electrolyte displays an initial CE of 84.4%, and then it increases to 99.6% after 30 cycles. Impressively, an average CE of 99.8% is maintained after 200 cycles. In sharp contrast, the cell in the 2 m W electrolyte shows rapid capacity decay and CE below 58% after 100 cycles, which could be attributed to the side reactions between H_2O and the Zn anode. Fig. 3b displays the typical Zn plating/stripping profiles. Stable voltage curves are characterized in W4D1, where the separation of charge and discharge potentials decreases initially and stabilizes at ~ 110 mV after 50 cycles. A



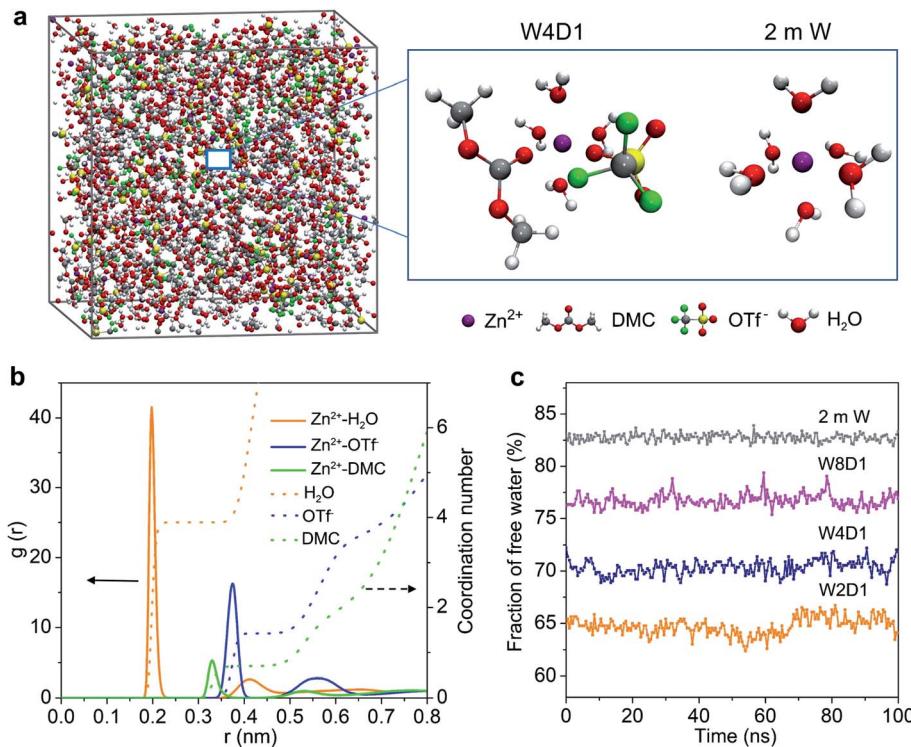


Fig. 2 MD studies of the Zn^{2+} solvation structure. (a) Snapshot of the MD simulation cell for the W4D1 electrolyte, and the representative Zn^{2+} -solvation structures in W4D1 and 2 m W electrolytes. (b) RDFs of Zn-O (H_2O), Zn-O (DMC) and Zn-O (OTf^-) pairs, and the coordination number in the W4D1 electrolyte. (c) Fraction of free water (not solvating to Zn^{2+}) in the H_2O + DMC electrolytes with a 100 ns simulation time.

lower CE with an unstable stripping process is observed in the 2 m W counterpart. Although the W2D1 electrolyte also affords stable cycling of Zn, the overpotential (~ 172 mV at the 50th cycle, Fig. S9, ESI[‡]) is much higher than that in W4D1, due to

the lower ionic conductivity. Typical charge/discharge profiles of Zn/Ti cells in W8D1 and W6D1 electrolytes (Fig. S10 and S11, ESI[‡]) suggest better performances than 2 m W but inferior stability to W4D1.

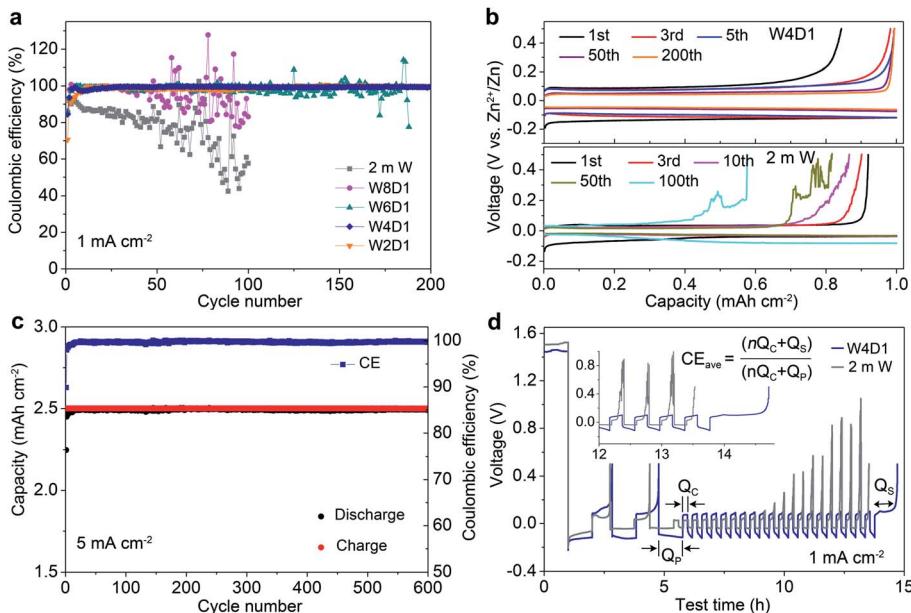


Fig. 3 Zn^{2+} plating/stripping behaviors in H_2O + DMC electrolytes. (a) Zn plating/stripping CE values of Zn/Ti cells in different electrolytes. (b) Typical voltage profiles of Zn/Ti cells in W4D1 and 2 m W at 1 mA cm^{-2} . (c) Cycling stability and Zn plating/stripping CE of the Zn/Ti cell in W4D1 at 5 mA cm^{-2} . (d) Evolution of voltage profiles of Zn/Ti cells in W4D1 and 2 m W electrolytes under a 'reservoir half-cell' method.

At a high current of 5.0 mA cm⁻² with an areal capacity of 2.5 mA h cm⁻², the Zn/Ti cell in W4D1 sustains durability over 600 cycles with a high average CE of 99.8% (Fig. 3c). Moreover, stable Zn plating/stripping plateaus without fluctuations are detected (Fig. S12, ESI‡), suggesting effective suppression of the side reactions on Zn (e.g., H₂ evolution and Zn passivation). Such good reversibility significantly stands out among those of the reported Zn anodes (Table S5, ESI‡). Fig. 3d shows the voltage profiles of Zn/Ti cells to further evaluate the reversibility of Zn plating/stripping in W4D1 and 2 m W electrolytes, according to the 'reservoir half-cell' protocol.²¹ The Zn/Ti cell firstly undergoes two cycles of charge/discharge to mitigate the substrate effects (e.g., lattice mismatch and interphase effects etc.) at 1 mA cm⁻² with an areal capacity of 1 mA h cm⁻² and an upper cut-off voltage of 0.5 V. Subsequently, 1 mA h cm⁻² of Zn (Q_p) is plated on Ti as a Zn reservoir, which is cycled at a fixed capacity of 0.2 mA h cm⁻² (Q_c). After n (e.g., 20) cycles, this cell is fully charged to 0.5 V to strip all removable Zn (Q_s). The average CE can be calculated by the equation $CE = (nQ_c + Q_s)/(nQ_c + Q_p)$. The W4D1 electrolyte supports significantly more stable plating/stripping and higher average CE than 2 m W (99.2% vs. 82.5%).

Furthermore, Zn/Zn symmetric cells were assembled to investigate Zn plating/stripping behaviors. The thickness of Zn foil is 50 μ m (areal capacity: \sim 29.2 mA h cm⁻²). Fig. 4a shows the voltage profiles at 1 mA cm⁻² with a discharge/charge time of 0.5 h. The cell with W4D1 exhibits a high cycling stability over 1000 h without any evident voltage hysteresis or overpotential

increase, in contrast to those in W8D1 and 2 m W with short lifespans and apparent voltage fluctuations. Enlarged discharge/charge curves are provided in Fig. S13 (ESI‡). The gradually reduced polarization in W4D1 during the initial 50 cycles is ascribed to the electrode activation process, as confirmed by the decrease of charge transfer resistance from electrochemical impedance spectroscopy (EIS, Fig. S14, ESI‡). At 5 mA cm⁻² with an areal capacity of 2.5 mA h cm⁻² (corresponding to \sim 8.5% depth of discharge (DOD)), the durability and reversibility of the Zn anode can be sustained up to 800 h in W4D1 (Fig. 4b and Fig. S15, ESI‡). Fig. 4c shows the rate capability of Zn/Zn cells with W4D1 and W2D1 electrolytes. The W4D1 cell delivers a stable and flat voltage plateau with a smaller increase of overpotential relative to the W2D1 cell (Fig. S16, ESI‡). Remarkably, as the current increases to 20 mA cm⁻², the cell sustains a high areal capacity of 10 mA h cm⁻² with a considerable DOD of 34.2% and low overpotential of \sim 270 mV. The electrochemical performance of the Zn/Zn cell in this H₂O + DMC system is competitive in comparison with those of recently reported Zn-based symmetric cells (Table S6, ESI‡).

Scanning electron microscopy (SEM) imaging demonstrates that the Zn electrode in the W4D1 electrolyte maintains a dense and smooth surface after 300 cycles at 1C (Fig. 4d). Impressively, a dendrite-free and uniform Zn surface is also characterized after 1050 cycles, ensuring the high stability of the Zn anode (Fig. S17, ESI‡). In sharp contrast, the cycled Zn electrode in the 2 m W electrolyte shows an uneven porous structure with cracks and dendrites (Fig. 4e). Moreover, there is no discernible by-

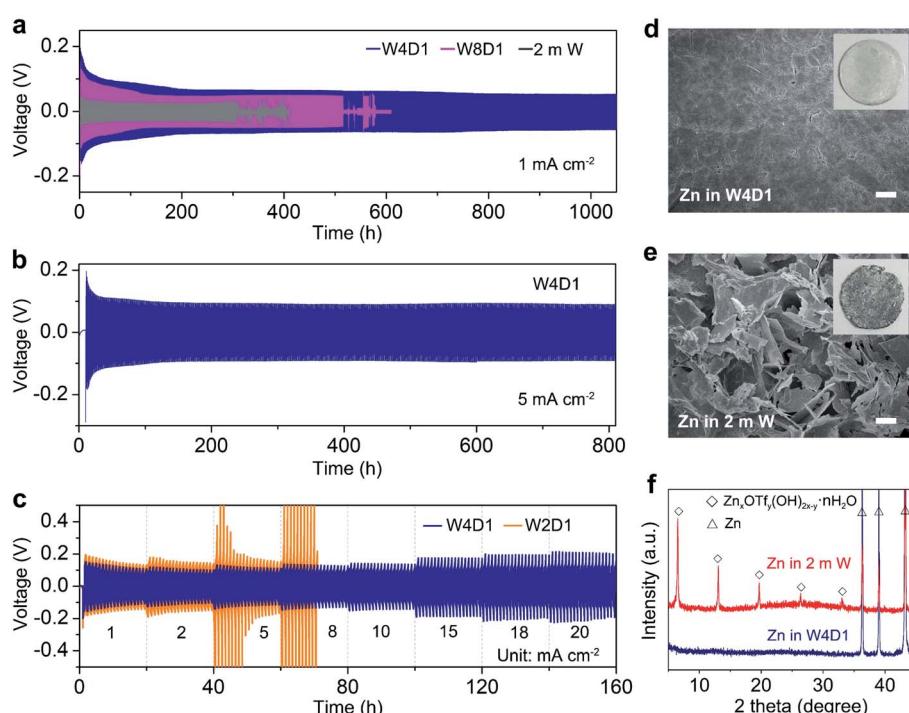


Fig. 4 Electrochemical test and characterization of Zn anodes in Zn/Zn cells. (a) Comparison of voltage profiles in W4D1, W8D1 and 2 m W electrolytes at 1 mA cm⁻². (b) Cycling performance in the W4D1 electrolyte at 5 mA cm⁻². (c) Rate capability of Zn/Zn cells with W4D1 and W2D1. (d, e) SEM images (scale bar, 10 μ m) and (f) XRD patterns of Zn anodes after 300 cycles. Insets of (d, e) show the optical images of cycled Zn anodes.



product in Zn after 300 cycles in W4D1, as evidenced by the X-ray diffraction (XRD) analysis (Fig. 4f), while, strong XRD signals related to the zinc triflate hydroxide hydrate ($Zn_xOTf_y(OH)_{2x-y} \cdot nH_2O$, ZOTH) are detected in 2 m W. The formation of ZOTH might follow a similar process to that of zinc sulfate hydroxide hydrate ($Zn_4SO_4(OH)_6 \cdot 5H_2O$), which has been often observed in aqueous $ZnSO_4$ electrolytes.^{30,38,46} Specifically, the H_2 evolution reaction leads to an increase of OH^- concentration in the vicinity of the electrode, triggering the precipitation reaction ($xZn^{2+} + yOTf^- + (2x-y)OH^- + nH_2O = Zn_xOTf_y(OH)_{2x-y} \cdot nH_2O$). Furthermore, the hydrophilicity of different electrolytes with respect to the Zn electrode was probed by contact angle measurements at ambient temperature (Fig. S18, ESI†). The initial contact angle of the W4D1 electrolyte on Zn foil is 58.7° , which drops to 36.2° after 1 min. Much higher contact angles are observed in 2 m W (initial 96.8° and 80.8° after 1 min). In addition, the contact angle of W4D1 on the cycled Zn is further decreased to 24.1° (Fig. S19, ESI†). The enhanced hydrophilicity would reduce the interfacial free energy between Zn and the electrolyte, favoring the homogeneous Zn^{2+} plating/stripping process.^{30,38}

Formation and composition of the SEI layer on the Zn anode

To analyze the influence of the Zn^{2+} -solvation structure on the formation mechanism and chemical composition of the SEI layer, DFT calculations were performed by adopting a cation-solvent/

anion complex model. The energy levels of the lowest unoccupied molecular orbital (LUMO) of the free DMC solvent and OTf^- anion are 0.77 and 2.42 eV, respectively. When Zn^{2+} is coordinated with DMC and OTf^- , their LUMO energy levels are significantly decreased to -2.75 and -2.79 eV, respectively (Fig. 5a). The cation-solvent or cation-anion complexes with a lower LUMO level indicate their easier electron reception from the anode than the free solvent/anion.^{43,47,48} The predicted reduction potentials of the free DMC solvent (-2.39 V) and free OTf^- anion (-2.46 V) are much lower than that of the Zn^{2+} /Zn redox couple (Fig. 5b). Thus, the reductive decomposition of free OTf^- (or free DMC) can hardly occur before Zn deposition, resulting in the absence of a protective SEI layer. With cation-solvent/anion coordination, the Zn^{2+} -DMC and Zn^{2+} - OTf^- complexes become reductively unstable below 0.47 and 0.14 V (vs. Zn^{2+} /Zn), where Zn^{2+} reduction will dominate, as further supported by the Mulliken charge analysis (Fig. S20, ESI†). It is well known that the electron could preferably transfer from the cation to the solvent (or anion) in the cation-solvent (or cation-anion) unit and induce the solvent/anion decomposition, where the SEI could be formed at the electrode interface.^{37,39,48} Herein, the introduction of the DMC solvent into the aqueous $Zn(OTf)_2$ electrolyte leads to a significant change of the Zn^{2+} solvation environment from a typical $Zn[H_2O]^{2+}$ (in 2 m W) to $Zn^{2+}[H_2O]_{3.9}[DMC]_{0.7}[OTf^-]_{1.4}$ (in W4D1). Accordingly, both coordinated DMC and OTf^- participate in the formation of the SEI on the Zn anode in W4D1.

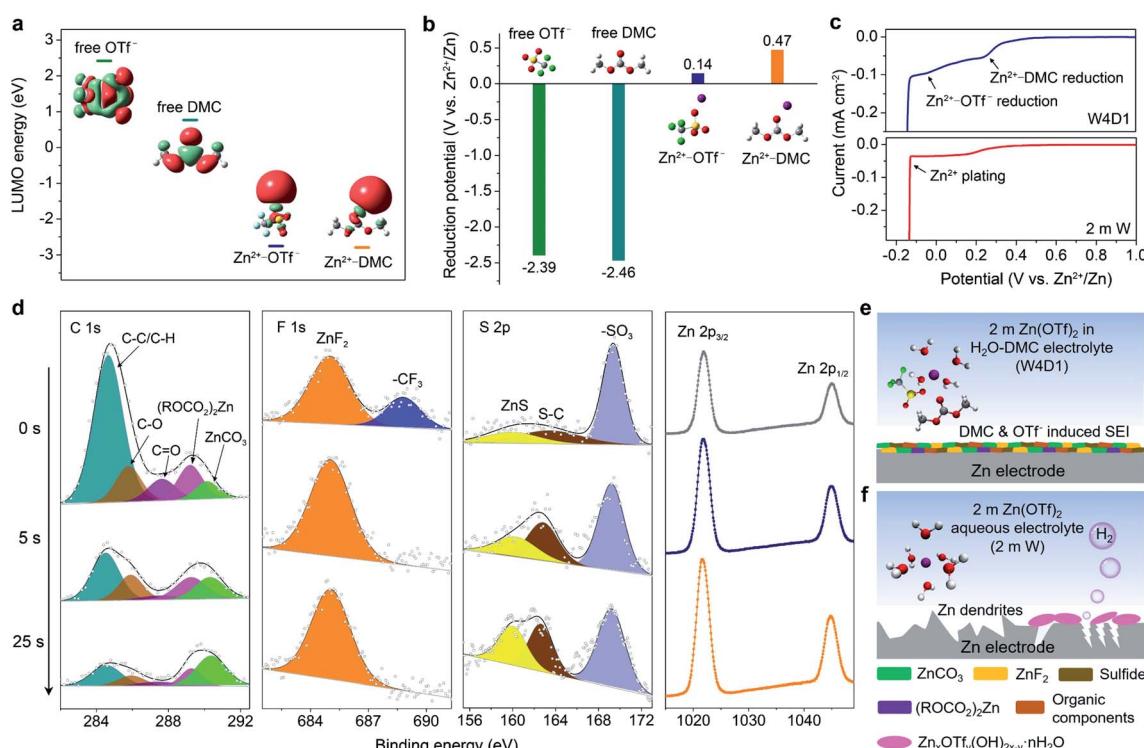


Fig. 5 SEI characterization on the Zn anode. (a) LUMO energy levels with corresponding LUMO isosurfaces and (b) the predicted reduction potential with geometric structures of the free OTf^- anion, free DMC solvent, and Zn^{2+} - OTf^- and Zn^{2+} -DMC coordinations from DFT calculations. (c) LSV profiles of W4D1 and 2 m W electrolytes at 5 mV s^{-1} . (d) XPS spectral regions for C 1s, F 1s, S 2p and Zn 2p with corresponding Ar^+ sputtering times on the Zn electrode in W4D1 after 10 cycles. Schematic illustration of the surface chemistry on the Zn electrode in (e) W4D1 and (f) 2 m W electrolytes.



To support the above mechanism, LSV measurements were conducted at 5 mV s^{-1} using a three-electrode configuration employing Ti foil as the working electrode, and Zn foil as the reference and counter electrodes (Fig. 5c and S21, ESI[‡]). The W4D1 electrolyte exhibits two discernible reduction peaks at ~ 0.3 and 0 V (vs. Zn^{2+}/Zn) prior to Zn^{2+} plating (around -0.14 V), corresponding to the stepwise reduction of the Zn^{2+} -DMC coordination and Zn^{2+} -OTf⁻ coordination, respectively. The difference of the reduction potential between the modeling and experimental data results from the overpotential in the practical cell. Besides, the decomposition of DMC could push back the reduction potential of OTf⁻. The preferential decomposition of DMC and OTf⁻ before Zn deposition in W4D1 would contribute to the *in situ* formation of an interphase on the Zn anode. In contrast, a much weaker current response with a broad peak at $\sim 0.15 \text{ V}$ in the 2 m W electrolyte indicates inefficient anion reduction.

The surface composition of the SEI formed on Zn after 10 cycles was analyzed by X-ray photoelectron spectroscopy (XPS, Fig. 5d). Compared with the C 1s spectrum in the 2 m W electrolyte (Fig. S22a, ESI[‡]), the signals related to organic $(\text{ROCO}_2)_2\text{Zn}$ (289.3 eV), inorganic ZnCO_3 (290.2 eV), and

etheral (C-O) species (285.8 eV) intensify strongly in W4D1, mainly arising from the decomposition of the Zn^{2+} -DMC complex. The reduction product of the DMC solvent is similar to that of DMC in a Li-based electrolyte.³⁹ The strong signal of C-C/C-H at the top layer mainly comes from the residual DMC and the adventitious carbon adsorbed on the substrate surface. After 25 s sputtering, the inorganic ZnCO_3 content increases largely from 4.25% to 39.7%. In the F 1s spectra, besides the $-\text{CF}_3$ species (688.8 eV) from either the incomplete reduction of OTf⁻ or the trace salt on the Zn surface, the distinct peak of inorganic ZnF_2 at 684.7 eV (ref. 3 and 37) is clearly observed in W4D1, which results from the decomposition of Zn^{2+} -OTf⁻ aggregates. When the top layer of the interphase is removed under Ar^+ sputtering, ZnF_2 becomes the dominant species. In sharp contrast, no apparent ZnF_2 signal can be detected on the cycled Zn anode in 2 m W (Fig. S22b, ESI[‡]). For the S 2p spectra, the signals of sulfide (e.g., ZnS)^{35,37} apparently appear as the Ar^+ sputtering time increases, further confirming the decomposition of the Zn^{2+} -OTf⁻ coordination and the involvement of decomposed species in the SEI formation. Additionally, the intensifying of the Zn peak coincides with the evolution of C and F signals,

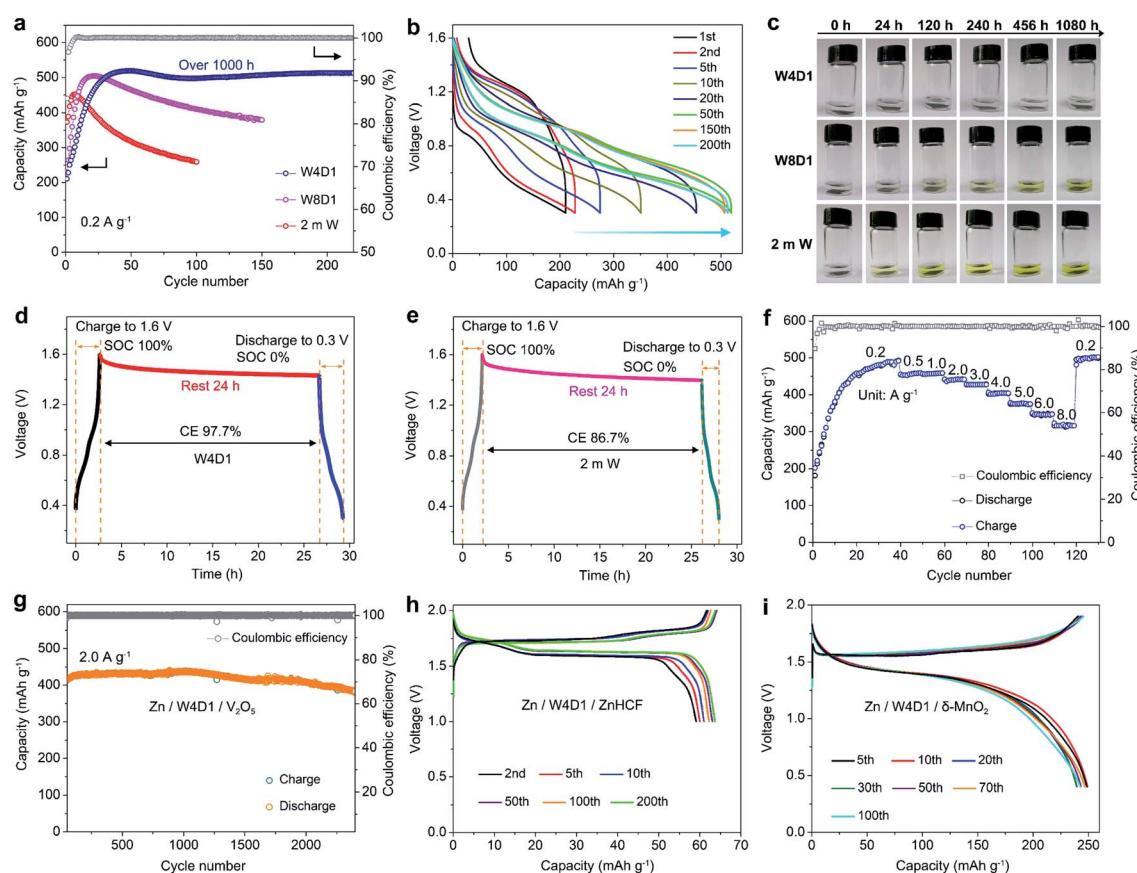


Fig. 6 Electrochemical performance of Zn-ion full batteries. (a) Cycling stability of $\text{Zn}/\text{V}_2\text{O}_5$ batteries in W4D1, W8D1, and 2 m W electrolytes at 0.2 A g^{-1} . (b) Selected charge/discharge profiles in W4D1. (c) Optical images of V_2O_5 electrodes immersed in W4D1, W8D1, and 2 m W solutions for different periods. Storage performance comparison of $\text{Zn}/\text{V}_2\text{O}_5$ batteries in (d) W4D1 and (e) 2 m W evaluated by resting for 24 h at 100% state of charge (SOC) at 0.2 A g^{-1} , followed by full discharge. (f) Rate capability. (g) Long-term cycling performance of the $\text{Zn}/\text{W4D1}/\text{V}_2\text{O}_5$ battery at 2.0 A g^{-1} . Typical discharge/charge profiles of the (h) $\text{Zn}/\text{W4D1}/\text{ZnHCF}$ battery at 50 mA g^{-1} and (i) $\text{Zn}/\text{W4D1}/\delta\text{-MnO}_2$ battery at 100 mA g^{-1} .



suggesting the enrichment of ZnCO_3 and ZnF_2 components in the inner SEI layer.

Consequently, the unique Zn^{2+} solvation structure in the W4D1 electrolyte enables the decomposition of Zn^{2+} -DMC and Zn^{2+} -OTf⁻ complexes and is involved in the formation of the SEI layer containing components such as ZnCO_3 , ZnF_2 , $(\text{ROCO}_2)_2\text{Zn}$, sulfide, organic compounds and/or their derivatives (Fig. 5e). The *in situ* generated interphase on the Zn anode in W4D1 suppresses H_2 evolution and Zn passivation and favors uniform Zn^{2+} electrodeposition, thus improving the reversibility and stability of the Zn electrode. In contrast, the 2 m W electrolyte cannot provide stable interface chemistry at the Zn electrode, leading to continuous parasitic reactions. After prolonged cycling, H_2 evolution increases the local pH on Zn, thus inducing the by-product generation of zinc triflate hydroxide hydrate (Fig. 5f and S23, ESI[‡]).

Electrochemical performance of Zn-ion full batteries

We then evaluated the application of this $\text{H}_2\text{O} + \text{DMC}$ electrolyte in Zn-ion full batteries composed of a Zn foil anode and different cathode materials (such as V_2O_5 , zinc hexacyanoferate (ZnHCF), and layered manganese dioxide ($\delta\text{-MnO}_2$)). Phase and morphology characterization studies of as-prepared V_2O_5 , ZnHCF, and $\delta\text{-MnO}_2$ are given in Fig. S24–S26 (ESI[‡]), respectively. Fig. 6a compares the cycling performances of Zn/ V_2O_5 batteries in W4D1, W8D1, and 2 m W electrolytes at 0.2 A g^{-1} . In W4D1, the V_2O_5 cathode delivers an initial discharge capacity of 210.5 mA h g^{-1} , which increases to 519.1 mA h g^{-1} with $\sim 100\%$ CE after 50 cycles. Impressively, the Zn/W4D1/ V_2O_5 system displays a reversible capacity of 512.9 mA h g^{-1} after 200 cycles (over 1000 h) with a high capacity retention of 98.8%. For comparison, the W8D1 electrolyte with a smaller amount of DMC moderately improves the stability of a Zn/ V_2O_5 battery with 410 mA h g^{-1} capacity after 100 cycles. As expected, the 2 m W cell displays a rapid capacity decay due to the severe dissolution of active materials. Fig. 6b shows the typical discharge/charge curves of a Zn/ V_2O_5 battery in the W4D1 electrolyte between 0.3 and 1.6 V. The gradual overpotential decrease and capacity increase upon cycling suggest an activation process of V_2O_5 and an increase of active mass utilization.^{15,49} An average discharge voltage plateau of 0.75 V is obtained at the 50th cycle, corresponding to an energy density of 415.2 $\text{W h kg}_{\text{cathode}}^{-1}$ and surpassing that of Zn/ V_2O_5 batteries in 2 m W and W8D1 electrolytes (Fig. S27 and S28, ESI[‡]).

To identify the solubility of electrode materials in electrolytes, the static soaking experiment was conducted by loading V_2O_5 electrodes in W4D1, W8D1, and 2 m W for different periods. As shown in Fig. 6c, the W4D1 electrolyte remains colorless and transparent after 1080 h of electrode immersion, whereas W8D1 and 2 m W turn light yellow after 120 h and 24 h, respectively. Additionally, parasitic reactions in Zn/ V_2O_5 cells were assessed by monitoring the open circuit voltage drop of a cell at the fully charged state and at the discharged state after 24 h of storage. A high CE of 97.7% is achieved in W4D1 (Fig. 6d), much higher than that in 2 m W (86.7%, Fig. 6e).

These comparative results indicate significant suppression of V_2O_5 dissolution in the hybrid electrolyte with an organic solvent.

The rate capability of Zn/W4D1/ V_2O_5 was recorded by progressively increasing the current densities from 0.2 to 8.0 A g^{-1} (Fig. 6f and S29, ESI[‡]). The first 40 cycles were tested at 0.2 A g^{-1} to activate the cell. Reversible capacities of 457, 440, 427, 404, 375, and 343 mA h g^{-1} are delivered at rates of 1.0, 2.0, 3.0, 4.0, 5.0, and 6.0 A g^{-1} , respectively. A high capacity of 319 mA h g^{-1} is achieved at 8.0 A g^{-1} . The average capacity recovers to 500 mA h g^{-1} as the rate resumes to 0.2 A g^{-1} . Besides, Fig. 6g shows the long-term cycling performance of the Zn/W4D1/ V_2O_5 cell at 2.0 A g^{-1} . The initial 50 cycles were tested at 0.5 A g^{-1} (Fig. S30a, ESI[‡]). A remarkable capacity of 381.9 mA h g^{-1} is achieved after 2400 cycles. The differential capacity (dQ/dV) curves exhibit two pairs of well overlapped broad peaks (Fig. S30b, c, ESI[‡]), further indicating the excellent reversibility. Note that the Zn anode (50 μm thickness) in the Zn/W4D1/ V_2O_5 cell is much more excessive, which compromises the whole energy density of the full cell. Thus, we attempted to estimate the battery performance on a more practical basis with a high-mass-loading V_2O_5 cathode ($\sim 11 \text{ mg cm}^{-2}$) and a thin Zn foil anode (20 μm thickness, $\sim 14.28 \text{ mg cm}^{-2}$). The assembled cell achieves a reversible capacity of 175 mA h g^{-1} with an energy density of 131 W h kg^{-1} based on the total mass of the anode and the cathode, and the DOD of the Zn anode reaches $\sim 37.7\%$ (Fig. S31, ESI[‡]).

In addition to V_2O_5 , full batteries pairing a Zn anode with ZnHCF and $\delta\text{-MnO}_2$ cathodes were assembled to demonstrate the universality of W4D1 for RAZB applications. The ZnHCF-based cell exhibits a high discharge voltage of 1.62 V and a stable capacity of 64 mA h g^{-1} with a 99% CE after 200 cycles at 50 mA g^{-1} (Fig. 6h and S32a, ESI[‡]). The $\delta\text{-MnO}_2$ cell delivers a reversible capacity of 243 mA h g^{-1} with an average discharge voltage of 1.35 V after 100 cycles at 100 mA g^{-1} (Fig. 6i and S32b, ESI[‡]). At a rate of 500 mA g^{-1} , the capacity retention reaches 89.5% after 500 cycles (Fig. S33, ESI[‡]). These results indicate the favorable compatibility between the W4D1 electrolyte and ZnHCF or $\delta\text{-MnO}_2$ cathode materials.

Conclusions

In summary, we report a non-concentrated aqueous electrolyte with the organic DMC additive to stabilize Zn electrochemistry. A Zn^{2+} -solvation structure with the co-contribution of the DMC solvent and OTf⁻ anion is found in the hybrid $\text{H}_2\text{O} + \text{DMC}$ electrolyte, as verified by structural and spectroscopic studies and MD simulations. This unique Zn^{2+} -solvation-sheath allows the formation of a $\text{ZnF}_2\text{-ZnCO}_3$ -rich SEI layer on the Zn electrode induced by the decomposition of Zn^{2+} -DMC and Zn^{2+} -OTf⁻ coordinations. As a result, parasitic reactions on the Zn anode are effectively suppressed, enabling reversible plating/stripping of Zn with 99.8% CE at 2.5 mA h cm^{-2} over 600 cycles and dendrite-free cycling of the Zn electrode over 1000 cycles. Furthermore, the formulated electrolyte (W4D1) consisting of 2 mol kg^{-1} $\text{Zn}(\text{OTf})_2$ in 4 $\text{H}_2\text{O} + 1\text{DMC}$ (molar ratio) features non-flammability and is



applicable to support the stable operation of full batteries that couple a Zn anode with diverse cathode materials (e.g., V_2O_5 , MnO_2 and ZnHCF). This work provides an alternative avenue to improve the performance of rechargeable Zn-based batteries. The strategy of addition of organic solvents can also inspire the design of efficient electrolytes for other aqueous battery chemistries.

Author contributions

N. Z. proposed the concept and supervised the work; Y. D. and N. Z. carried out the experimental design, characterization and electrochemical measurements; Y. D., G. M. and S. D. prepared the cathode materials; L. M. performed the theoretical simulations; N. Z. wrote the manuscript; Y. W., L. W. and J. X. helped to discuss and analyze the data; all authors discussed and revised the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (22075067 and 21805066), Natural Science Foundation of Hebei Province (B202001001 and B2019201160), Top Young Talents Project of Hebei Education Department (BJ2019052), Advanced Talents Incubation Program of Hebei University (521000981138), and Chunhui Program of the Ministry of Education of China.

References

- 1 N. Zhang, X. Chen, M. Yu, Z. Niu, F. Cheng and J. Chen, *Chem. Soc. Rev.*, 2020, **49**, 4203–4219.
- 2 L. E. Blanc, D. Kundu and L. F. Nazar, *Joule*, 2020, **4**, 771–799.
- 3 L. Ma, T. P. Pollard, Y. Zhang, M. A. Schroeder, M. S. Ding, A. V. Cresce, R. Sun, D. R. Baker, B. A. Helms, E. J. Maginn, C. Wang, O. Borodin and K. Xu, *Angew. Chem., Int. Ed.*, 2021, DOI: 10.1002/anie.202017020.
- 4 Q. Yang, Q. Li, Z. Liu, D. Wang, Y. Guo, X. Li, Y. Tang, H. Li, B. Dong and C. Zhi, *Adv. Mater.*, 2020, **32**, 2001854.
- 5 J. Shin, J. Lee, Y. Park and J. W. Choi, *Chem. Sci.*, 2020, **11**, 2028–2044.
- 6 D. Chao, W. Zhou, F. Xie, C. Ye, H. Li, M. Jaroniec and S. Qiao, *Sci. Adv.*, 2020, **6**, eaba4098.
- 7 A. Konarov, N. Voronina, J. H. Jo, Z. Bakenov, Y.-K. Sun and S.-T. Myung, *ACS Energy Lett.*, 2018, **3**, 2620–2640.
- 8 H. Pan, Y. Shao, P. Yan, Y. Cheng, K. S. Han, Z. Nie, C. Wang, J. Yang, X. Li, P. Bhattacharya, K. T. Mueller and J. Liu, *Nat. Energy*, 2016, **1**, 16039.
- 9 D. Chao, W. Zhou, C. Ye, Q. Zhang, Y. Chen, L. Gu, K. Davey and S.-Z. Qiao, *Angew. Chem., Int. Ed.*, 2019, **58**, 7823–7828.
- 10 J. Wang, J.-G. Wang, H. Liu, C. Wei and F. Kang, *J. Mater. Chem. A*, 2019, **7**, 13727–13735.
- 11 L. Ma, S. Chen, C. Long, X. Li, Y. Zhao, Z. Liu, Z. Huang, B. Dong, J. A. Zapien and C. Zhi, *Adv. Energy Mater.*, 2019, **9**, 1902446.
- 12 R. Trócoli and F. La Mantia, *ChemSusChem*, 2015, **8**, 481–485.
- 13 Y. Yang, Y. Tang, G. Fang, L. Shan, J. Guo, W. Zhang, C. Wang, L. Wang, J. Zhou and S. Liang, *Energy Environ. Sci.*, 2018, **11**, 3157–3162.
- 14 C. Xia, J. Guo, Y. Lei, H. Liang, C. Zhao and H. N. Alshareef, *Adv. Mater.*, 2018, **30**, 1705580.
- 15 N. Zhang, Y. Dong, M. Jia, X. Bian, Y. Wang, M. Qiu, J. Xu, Y. Liu, L. Jiao and F. Cheng, *ACS Energy Lett.*, 2018, **3**, 1366–1372.
- 16 P. Hu, T. Zhu, X. Wang, X. Wei, M. Yan, J. Li, W. Luo, W. Yang, W. Zhang, L. Zhou, Z. Zhou and L. Mai, *Nano Lett.*, 2018, **18**, 1758–1763.
- 17 A. Khayum M, M. Ghosh, V. Vijayakumar, A. Halder, M. Nurhuda, S. Kumar, M. Addicoat, S. Kurungot and R. Banerjee, *Chem. Sci.*, 2019, **10**, 8889–8894.
- 18 Z. Guo, Y. Ma, X. Dong, J. Huang, Y. Wang and Y. Xia, *Angew. Chem., Int. Ed.*, 2018, **57**, 11737–11741.
- 19 W. Yang, X. Du, J. Zhao, Z. Chen, J. Li, J. Xie, Y. Zhang, Z. Cui, Q. Kong, Z. Zhao, C. Wang, Q. Zhang and G. Cui, *Joule*, 2020, **4**, 1557–1574.
- 20 Q. Zhao, W. Huang, Z. Luo, L. Liu, Y. Lu, Y. Li, L. Li, J. Hu, H. Ma and J. Chen, *Sci. Adv.*, 2018, **4**, eaao1761.
- 21 L. Ma, M. A. Schroeder, O. Borodin, T. P. Pollard, M. S. Ding, C. Wang and K. Xu, *Nat. Energy*, 2020, **5**, 743–749.
- 22 L. Ma, S. Chen, X. Li, A. Chen, B. Dong and C. Zhi, *Angew. Chem., Int. Ed.*, 2020, **59**, 23836–23844.
- 23 S.-B. Wang, Q. Ran, R.-Q. Yao, H. Shi, Z. Wen, M. Zhao, X.-Y. Lang and Q. Jiang, *Nat. Commun.*, 2020, **11**, 1634.
- 24 Q. Zhang, J. Luan, L. Fu, S. Wu, Y. Tang, X. Ji and H. Wang, *Angew. Chem., Int. Ed.*, 2019, **58**, 15841–15847.
- 25 Z. Kang, C. Wu, L. Dong, W. Liu, J. Mou, J. Zhang, Z. Chang, B. Jiang, G. Wang, F. Kang and C. Xu, *ACS Sustainable Chem. Eng.*, 2019, **7**, 3364–3371.
- 26 Y. Zeng, X. Zhang, R. Qin, X. Liu, P. Fang, D. Zheng, Y. Tong and X. Lu, *Adv. Mater.*, 2019, **31**, 1903675.
- 27 Q. Yang, Y. Guo, B. Yan, C. Wang, Z. Liu, Z. Huang, Y. Wang, Y. Li, H. Li, L. Song, J. Fan and C. Zhi, *Adv. Mater.*, 2020, **32**, 2001755.
- 28 X. Xie, S. Liang, J. Gao, S. Guo, J. Guo, C. Wang, G. Xu, X. Wu, G. Chen and J. Zhou, *Energy Environ. Sci.*, 2020, **13**, 503–510.
- 29 H. Yang, Z. Chang, Y. Qiao, H. Deng, X. Mu, P. He and H. Zhou, *Angew. Chem., Int. Ed.*, 2020, **59**, 9377–9381.
- 30 J. Hao, X. Li, S. Zhang, F. Yang, X. Zeng, S. Zhang, G. Bo, C. Wang and Z. Guo, *Adv. Funct. Mater.*, 2020, **30**, 2001263.
- 31 Y. Dong, S. Di, F. Zhang, X. Bian, Y. Wang, J. Xu, L. Wang, F. Cheng and N. Zhang, *J. Mater. Chem. A*, 2020, **8**, 3252–3261.
- 32 A. Naveed, H. Yang, J. Yang, Y. Nuli and J. Wang, *Angew. Chem., Int. Ed.*, 2019, **58**, 2760–2764.
- 33 C. Zhang, J. Holoubek, X. Wu, A. Daniyar, L. Zhu, C. Chen, D. P. Leonard, I. A. Rodríguez-Pérez, J.-X. Jiang, C. Fang and X. Ji, *Chem. Commun.*, 2018, **54**, 14097–14099.



34 R. Qin, Y. Wang, M. Zhang, Y. Wang, S. Ding, A. Song, H. Yi, L. Yang, Y. Song, Y. Cui, J. Liu, Z. Wang, S. Li, Q. Zhao and F. Pan, *Nano Energy*, 2021, **80**, 105478.

35 L. Cao, D. Li, E. Hu, J. Xu, T. Deng, L. Ma, Y. Wang, X.-Q. Yang and C. Wang, *J. Am. Chem. Soc.*, 2020, **142**, 21404–21409.

36 F. Wang, O. Borodin, T. Gao, X. Fan, W. Sun, F. Han, A. Faraone, J. A. Dura, K. Xu and C. Wang, *Nat. Mater.*, 2018, **17**, 543–549.

37 H. Qiu, X. Du, J. Zhao, Y. Wang, J. Ju, Z. Chen, Z. Hu, D. Yan, X. Zhou and G. Cui, *Nat. Commun.*, 2019, **10**, 5374.

38 J. Hao, L. Yuan, C. Ye, D. Chao, K. Davey, Z. Guo and S. Qiao, *Angew. Chem., Int. Ed.*, 2021, **60**, 7366–7375.

39 K. Xu, *Chem. Rev.*, 2014, **114**, 11503–11618.

40 J.-B. Brubach, A. Mermet, A. Filabozzi, A. Gerschel, D. Lairez, M. P. Krafft and P. Roy, *J. Mater. Chem. B*, 2001, **105**, 430–435.

41 J. Zhao, J. Zhang, W. Yang, B. Chen, Z. Zhao, H. Qiu, S. Dong, X. Zhou, G. Cui and L. Chen, *Nano Energy*, 2019, **57**, 625–634.

42 N. Chang, T. Li, R. Li, S. Wang, Y. Yin, H. Zhang and X. Li, *Energy Environ. Sci.*, 2020, **13**, 3527–3535.

43 F. Wang, O. Borodin, M. S. Ding, M. Gobet, J. Vatamanu, X. Fan, T. Gao, N. Eidson, Y. Liang, W. Sun, S. Greenbaum, K. Xu and C. Wang, *Joule*, 2018, **2**, 927–937.

44 O. Borodin, M. Olguin, P. Ganesh, P. R. C. Kent, J. L. Allen and W. A. Henderson, *Phys. Chem. Chem. Phys.*, 2016, **18**, 164–175.

45 L. Suo, O. Borodin, Y. Wang, X. Rong, W. Sun, X. Fan, S. Xu, M. A. Schroeder, A. V. Cresce, F. Wang, C. Yang, Y.-S. Hu, K. Xu and C. Wang, *Adv. Energy Mater.*, 2017, **7**, 1701189.

46 Y. Dong, M. Jia, Y. Wang, J. Xu, Y. Liu, L. Jiao and N. Zhang, *ACS Appl. Energy Mater.*, 2020, **3**, 11183–11192.

47 X. Chen, X. Shen, T.-Z. Hou, R. Zhang, H.-J. Peng and Q. Zhang, *Chem.*, 2020, **6**, 2242–2256.

48 Z. Hou, M. Dong, Y. Xiong, X. Zhang, Y. Zhu and Y. Qian, *Adv. Energy Mater.*, 2020, **10**, 1903665.

49 N. Zhang, M. Jia, Y. Dong, Y. Wang, J. Xu, Y. Liu, L. Jiao and F. Cheng, *Adv. Funct. Mater.*, 2019, **29**, 1807331.

