Materials Advances



PAPER View Article Online
View Journal | View Issue



Cite this: *Mater. Adv.*, 2024, 5, 749

Received 27th October 2023,

Accepted 4th December 2023 DOI: 10.1039/d3ma00915q

rsc.li/materials-advances

2D/2D Z-scheme $WO_3/g-C_3N_4$ heterojunctions for photocatalytic organic pollutant degradation and nitrogen fixation[†]

Yasi Li 📭 and Junkai Wang*

Two-dimensional/two-dimensional (2D/2D) Z-scheme $WO_3/g-C_3N_4$ heterojunctions were successfully prepared by facile rapid calcination, which exhibited considerable photocatalytic performance in environmental application and energy application without any cocatalyst. The synthesized 2D/2D Z-scheme WO₃/q-C₃N₄ significantly improved the visible-light photocatalytic degradation of tetracycline hydrochloride (TC-HCl), and 40%WO₃/g-C₃N₄ had the best photocatalytic degradation effect. 40%WO₃/ $q-C_xN_4$ could also degrade rhodamine B (RhB), methylene blue (MB) and methyl orange (MO), and RhB was almost completely degraded after 20 min irradiation. ${}^{ullet}O_2^-$ was the main active species in the degradation process of 40%WO₃/g-C₃N₄. The 2D/2D Z-scheme heterostructure enhanced the photogenerated electron-hole separation and transfer ability and possessed good photocatalytic stability. The 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunction system was first used in nitrogen fixation. 40%WO₃/q-C₃N₄ can simultaneously achieve photocatalytic nitrogen reduction reaction (NRR) and nitrogen oxidation reaction (NOR) to produce NH₄⁺ and NO₃⁻, respectively, using air as a nitrogen source. However, in the presence of a hole sacrificial agent and N2 as a nitrogen source, the photocatalytic nitrogen fixation reaction of 40%WO₃/g-C₃N₄ was dominated by NRR. The nitrogen fixation products and their possible mechanisms were also discussed. This study confirms that the designed 2D/2D Z-scheme WO₃/q-C₃N₄ heterojunctions have great potential in the photocatalytic degradation of different-type organic pollutants and regulable photocatalytic NRR and NOR reactions.

Introduction

Environmental safety and energy resources are among the primary needs for human survival and development. Photocatalysis is regarded as one of the most hopeful methods for environment remediation and energy conversion because of its mild reaction conditions, no secondary pollution, and low energy consumption. ¹⁻⁴ Under light irradiation, the semiconductor photocatalysts are excited to produce photogenerated carriers, which can directly or indirectly participate in the oxidation–reduction reaction. ¹⁻⁴ Among the visible-light catalytic materials, WO₃ and g-C₃N₄ photocatalytic materials have the advantages of a suitable energy band structure, good visible-light response range, and relatively simple preparation process. ⁵⁻⁷ Therefore, WO₃ and g-C₃N₄ are ideal materials for constructing efficient visible-light catalysts. Furthermore, if the

Industrial manufacturing, agricultural production, and daily life produce much wastewater. Organic pollutants in wastewater are toxic, accumulative, and challenging to degrade even at low concentrations, posing a serious threat to the water environment.¹⁷ There are a variety of organic pollutants with

two materials are integrated to construct type-II or Z-scheme heterojunctions, the electrons (e⁻) and holes (h⁺) can be physically separated, favoring the redox reaction. 19,20 In addition, the Z-scheme can simultaneously use the more positive valence band (VB) of one semiconductor and the more negative conduction band (CB) of the other semiconductor, so it has a stronger redox capacity than the one-component semiconductor.8-16 Two-dimensional/two-dimensional (2D/2D) composite structures have the largest interface contact area, which is conducive to photogenerated carrier transmission. 9-16 Therefore, 2D/2D Z-scheme heterojunctions can effectively enhance the performance of WO₃/g-C₃N₄ photocatalysts. The reported 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunction systems had complex synthesis, insufficient application research, need for cocatalyst and other deficiencies to some degree. 9-16 Thus, it is necessary to further study the 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunction in more ways.

^a Department of Mechanical Engineering, College of Engineering, Shantou University, Shantou 515063, China

b College of Chemistry and Chemical Engineering, Shantou University, Shantou 515063, China. E-mail: jkwang@stu.edu.cn

[†] Electronic supplementary information (ESI) available. See DOI: https://doi.org/10.1039/d3ma00915g

Paper Materials Advances

various properties in environmental water bodies, such as organic dyes, antibiotics, surfactants, and endocrine disruptors. ^{17–19} Tetracycline hydrochloride (TC-HCl) has been widely used in humans and animals as an inexpensive broad-spectrum antibiotics. ^{20–23} TC-HCl easily accumulates in water and soil systems because of its excellent water solubility and long half-life. ^{20–23} Organic dyes are common organic pollutants, and the same method has different removal effects on dyes with different properties. ²⁴ The traditional removal methods of organic pollutants in the water include physical adsorption, chemical oxidation, and biodegradation. However, most of them have the disadvantages of poor efficiency, complicated methods, high cost, or easily causes secondary pollution. ^{16,21–23} The degradation of different-type organic pollutants in water is an urgent problem to be solved.

Moreover, nitrogen is an indispensable component of the biological structure. 25-27 It is found in proteins and nucleic acids, and most organisms except nitrogen-fixing microorganisms cannot directly use N2. 25,28,29 Nitrogen fixation is the conversion of N2 to simple nitrogenous compounds (nitric oxide, ammonia and others), followed by the generation of more complex compounds that can be used by organisms.^{29,30} In recent years, NH3 has become a crucial raw material and green energy carrier. 28 Nevertheless, the traditional Haber-Bosch process remains the dominant industrial NH₃ production method, which consumes excessive fossil and releases harmful gases. 25,28,30-33 HNO₃ is also a vital raw material in agriculture, military, chemical industry and other areas.34,35 However, the industrial HNO3 is synthesized by the Ostwald process through catalytic oxidation of NH₃, so this method is highly energy-consuming. 31,32,34,35 At present, most of the new methods of artificial nitrogen fixation are to reduce N₂ to produce NH₃. However, there are few studies on the oxidation of N2 to produce HNO3 or N2 disproportionation reaction. Therefore, developing eco-friendly and low-cost methods to fix N₂ by directly forming NH₃ and HNO₃ is of great interest. 34,35

In this paper, 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunctions with different doping ratios were prepared using ice water bath ultrasonography and rapid calcination. The degradation effects on typical antibiotic organic pollutants (TC-HCl) and typical dye organic pollutants with different charge properties [amphoteric dye rhodamine B (RhB), cationic dye methylene blue (MB), and anionic dye methyl orange (MO)] were explored. The performance of photocatalytic nitrogen fixation (NRR and NOR) was investigated using two typical photocatalytic nitrogen fixation conditions. According to the experimental results, the possible mechanisms of the photocatalytic degradation and photocatalytic nitrogen fixation were proposed, which offered a reference for preparing 2D/2D Z-scheme heterojunction photocatalysts and photocatalytic degradation and nitrogen fixation.

Experimental

Materials

Sodium tungstate dihydrate ($Na_2WO_4 \cdot 2H_2O$), potassium sodium tartrate tetrahydrate ($C_4H_4KNaO_6 \cdot 4H_2O$), and sodium hydroxide (NaOH) were obtained from Sinopharm Chemical Reagent Co.,

Ltd. Tetracycline hydrochloride (TC-HCl), rhodamine B (RhB), methylene blue (MB), methyl orange (MO), ammonium oxalate (AO), ammonium chloride (NH $_4$ Cl), potassium nitrate (KNO $_3$) and potassium mercury iodide (K $_2$ HgI $_4$) were acquired from Shanghai Maclin Biochemical Co., Ltd. Isopropyl alcohol (IPA), ethanol and methanol were obtained from Beijing Chemical Plant. 65% Nitric acid was derived from Beijing Chemical Plant. Melamine (chemically pure, content $\geq 98\%$) was purchased from Sigma Aldrich (Shanghai) Trading Co., Ltd. High purity nitrogen (content $\geq 99.999\%$) and compressed air were acquired from Beijing Millennium Capital Gas Co., Ltd. All solutions in this paper were prepared using ultra-pure water.

Synthesis of 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunctions

400 mg of Na₂WO₄·2H₂O was added into 300 mL of 4.8 M nitric acid at room temperature for 72 h, centrifugally washed and dried, and ground into a yellow powder as the WO₃·2H₂O precursor. ³⁴ 10 g melamine was put into a covered crucible and calcined at 550 °C (heating rate: 5 °C min⁻¹) in a muffle furnace for 4 h. After air cooling, it was ground into a light yellow powder as Bulk g-C₃N₄. ³⁶

500 mg of Bulk g- C_3N_4 was mixed with WO $_3\cdot 2H_2O$ of different masses in 20 mL ethanol, ultrasonicated in an ice water bath for 12 h, stirred for 1 hour, and completely dried. The sample underwent rapid calcination at 400 °C for 0.5 h, and was fully ground to obtain the 2D/2D Z-scheme WO $_3$ /g- C_3N_4 heterojunctions. WO $_3$ in the WO $_3$ /g- C_3N_4 composite is the final product of 10 wt.%, 20 wt.%, 30 wt.%, 40 wt.% and 50 wt.%, respectively. They were named as 10% WO $_3$ /g- C_3N_4 , 20% WO $_3$ /g- C_3N_4 , 30% WO $_3$ /g- C_3N_4 , 40% WO $_3$ /g- C_3N_4 and 50% WO $_3$ /g- C_3N_4 . Pure WO $_3$ and pure g- C_3N_4 were prepared for comparison experiments.

Photocatalytic degradation evaluation

The light source was a 300 W Xenon lamp (HX-UV300, Beijing NBET Technology Co., Ltd) equipped with a UVCUT420 ($\lambda \geq$ 420) UV cut-off filter. The optical power meter (CEL-NP2000) monitored the light intensity, and the light intensity was controlled at 100 mW cm⁻².

This work used antibiotic organic pollutants TC-HCl and dye organic pollutants MB, RhB and MO as photocatalytic degradation targets. The characteristic peaks of TC-HCl, RhB, MB and MO were 357 nm, 554 nm, 664 nm and 463 nm, $^{37-39}$ respectively. The 30 mg photocatalyst was dispersed in 100 mL aqueous solution containing 10 mg L $^{-1}$ organic pollutants, and stirred away from light for 30 min to achieve the adsorption–desorption equilibrium. After the visible-light source was turned on, a 3 mL suspension was taken at certain intervals for centrifugation, and the absorbance of the organic pollutants after degradation was determined by UV-Vis spectrophotometer (YOKE T3202). The degradation efficiency (η) was calculated using the characteristic peak absorbance value. The η was calculated by the eqn (1):³⁸

$$\eta = \frac{A_0 - A}{A_0} \times 100\% = \frac{C_0 - C}{C_0} \times 100\% \tag{1}$$

Materials Advances Paper

where A_0 and A are the initial absorbance of the characteristic peak of organic pollutants and the absorbance after a certain reaction time, respectively. According to the Lambert-Beer law, C_0 and C are the initial concentration of organic pollutants and the concentration after a certain time, respectively.

Photocatalytic nitrogen fixation evaluation

Experiment 1 and Experiment 2 are two typical conditions of the photocatalytic nitrogen fixation reaction. 34,40,41 The light source was 300 W Xenon lamp (HSX-UV300).

Experiment 1: a 100 mg quantity of photocatalyst was dispersed in 100 mL ultra-pure water, and then ultrasonicated for 15 min. Air flowed into the above suspension at a rate of 100 mL min⁻¹. The suspension was taken at set intervals to test the concentration of NH₄⁺ and NO₃⁻.34,41

Experiment 2: a 100 mg quantity of photocatalyst was dispersed in 100 mL 20% methanol aqueous solution, and then ultrasonicated for 15 min. N2 flowed into the above suspension at a rate of 100 mL min⁻¹. The suspension was taken at set intervals to test the concentration of NH₄⁺ and $NO_3^{-40,41}$

The concentration of NH₄⁺ was determined by Nessler's reagent colorimetric method. The concentration of NO₃ was measured by ion chromatography (Shimadzu LC20Adsp, Shodex IC SI-52 4E). The above methods were referred to in our previous paper.41

Results and discussion


Photocatalyst characterization

X-ray diffraction spectra (XRD, Rigaku D/MAX-2550V) (Fig. 1(a)) and Fourier-transform infrared (FT-IR, BRUKER VERTEX70) spectra (Fig. 1(b)) were used to characterize the chemical composition and structure of the g-C₃N₄, WO₃ and WO₃/ g-C₃N₄ composites. In Fig. 1(a), the characteristic peaks at 13.1° and 27.4° belong to the (100) and (002) crystal faces of pure g- C_3N_4 (JCPDS 87-1526), ^{33,42} respectively. The (002) peak is

attributed to the stacking structure of the conjugated aromatic rings, while the (100) peak is attributed to the interlayer stacking of g-C₃N₄. 43,44 Therefore, after g-C₃N₄ was peeled off by ultrasonic treatment, the intensity of the (100) peak gradually broadened and weakened until it disappeared. The characteristic peaks of pure WO₃ are in accordance with JCPDS 83-0950, which belongs to monoclinic WO₃ (m-WO₃). The XRD results of WO₃/g-C₃N₄ contain the characteristic peaks of g-C₃N₄ and WO₃. With the increase of WO₃ doping amount, the peaks of WO3 become stronger, while the peaks of g-C3N4 become weaker. The XRD results indicate that the WO₃/g-C₃N₄ composites were prepared successfully. These materials maintain the complete crystal structure of the sheet-like g-C3N4 and WO3.

As shown in Fig. 1(b), the FT-IR spectrum of pure WO₃ has a wide peak at 631 cm⁻¹ due to the stretching vibration of the O-W-O bond. 46 The peak of pure g-C₃N₄ at 803 cm⁻¹ was ascribed to the out-of-plane bending vibration of the 3-Striazine ring. The peaks at 1230 cm⁻¹, 1313 cm⁻¹, 1395 cm⁻¹, 1537 cm⁻¹ and 1633 cm⁻¹ belong to the skeleton stretching vibration of the C-N heterocyclic ring. 42 All signals of g-C₃N₄ can be seen in the FT-IR spectra of WO₃/g-C₃N₄. With the increase of the WO3 doping amount, the characteristic peaks of WO3 gradually become stronger. This is consistent with the XRD results, and indicates the structural integrity of the WO₃/g-C₃N₄ composite.

X-ray photoelectron spectroscopy (XPS, Thermo Fisher Scientific ESCALAB250Xi) was applied to study the surface element composition and valence information of the photocatalysts. Fig. 2(a) shows the XPS full spectrum of g-C₃N₄, WO₃ and 40%WO₃/g-C₃N₄. The XPS survey spectrum of 40%WO₃/ g-C₃N₄ shows four elements (C, N, O and W), and no other impurities appear. The C and N are provided by g-C₃N₄, and O and W are provided by WO₃. Fig. 2(b) is the high-resolution W 4f spectrum of WO₃ and 40%WO₃/g-C₃N₄. Compared with the two peaks of pure WO₃ (36.0 eV and 38.1 eV), the two peaks of 40%WO₃/g-C₃N₄ shift to lower binding energy (35.6 eV and 37.7 eV). The reason for this shift may be that the hydrogen

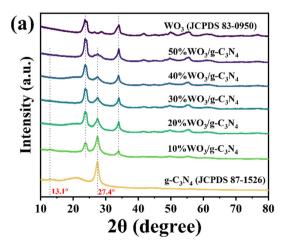

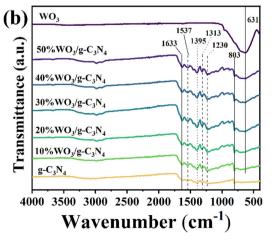


Fig. 1 (a) XRD and (b) FT-IR spectra of the $g-C_3N_4$, WO_3 and $WO_3/g-C_3N_4$ composites

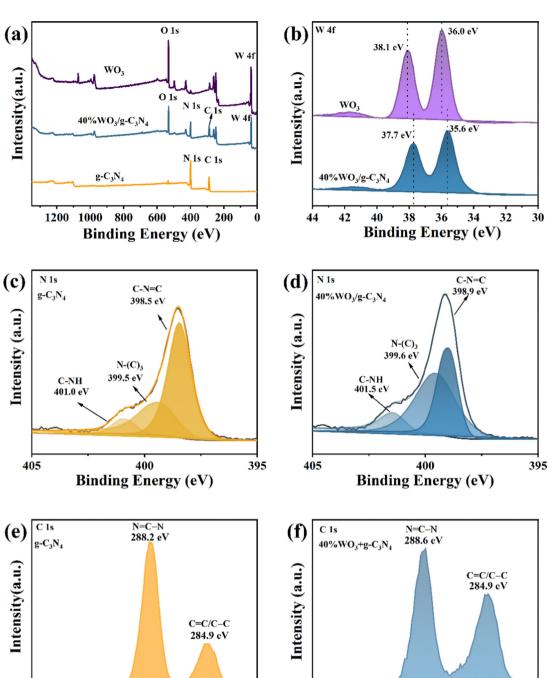


Fig. 2 (a) XPS survey spectra of $g-C_3N_4$ and $40\%WO_3/g-C_3N_4$, (b) high-resolution W 4f spectra of WO_3 and $40\%WO_3/g-C_3N_4$, (c) high-resolution N1s spectra of $g-C_3N_4$, (d) high-resolution N1s spectra of $40\%WO_3/g-C_3N_4$, (e) high-resolution C1s spectra of $g-C_3N_4$ and (f) high-resolution C1s spectra of $40\%WO_3/g-C_3N_4$.

294

292

290

288

Binding Energy (eV)

286

284

282

282

bond formed between the terminal –NH $_2$ and W–O bond during the action of WO $_3$ and g-C $_3$ N $_4$ will slightly weaken the W–O bond, thus reducing the binding energy value of W 4f in 40% WO $_3$ /g-C $_3$ N $_4$. ^{47,48} Fig. 2(c) and (d) show the high-resolution N 1s spectra of g-C $_3$ N $_4$ and 40%WO $_3$ /g-C $_3$ N $_4$, respectively. The positions of the three N1s peaks of pure g-C $_3$ N $_4$ are 398.5 eV,

294

292

290

288

Binding Energy (eV)

286

284

399.5 eV and 401.0 eV, which can be attributed to C-N=C, N- $(C)_3$ and C-NH, ⁴⁹ respectively. The N 1s peaks of 40%WO₃/g-C₃N₄ are shifted towards higher binding energy due to the charge transfer at the interface of WO₃ and g-C₃N₄. ⁵⁰ This illustrates that a heterostructure is formed between g-C₃N₄ and WO₃. Fig. 2(e) and (f) show the high-resolution C 1s

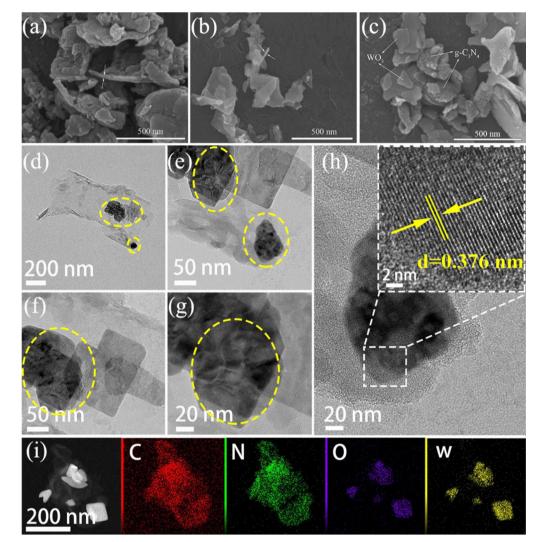


Fig. 3 SEM images of (a) $g-C_3N_4$, (b) WO_3 and (c) $40\%WO_3/g-C_3N_4$; (d)–(h) HRTEM images and (i) EDS mapping images of $40\%WO_3/g$ C_3N_4 .

spectra of g-C₃N₄ and 40%WO₃/g-C₃N₄, respectively. 40%WO₃/ g-C₃N₄ has two major C 1s peaks at 284.9 eV and 288.6 eV, corresponding to sp² bonded carbon (N=C-N) and aromatic carbon (C=C/C-C), 19 while the corresponding peaks positions for pure g-C₃N₄ are 284.9 eV and 288.2 eV, respectively. Compared to g-C₃N₄, the position of 40%WO₃/g-C₃N₄ was slightly shifted by 0.4 eV. 50 This is consistent with the results of N1s, verifying the existence of the heterojunction.

The surface morphology of g-C₃N₄, WO₃ and 40%WO₃/g-C₃N₄ can be visually displayed through scanning electron microscope (SEM, Hitachi SU8010) and high-resolution transmission electron microscope (HRTEM, JEOL JEM-F200) with an energy dispersive spectrometer (EDS). As shown by the white arrow in Fig. 3(a), g-C₃N₄ is a stack of nanosheets with a thickness of less than 30 nm. WO₃ is composed of WO₃ nanosheets, which are indicated by the white arrow in Fig. 3(b). Fig. 3(c) shows that 40%WO₃/ g-C₃N₄ is a 2D composite structure formed by stacking g-C₃N₄ nanosheets and WO3 nanosheets together.

Fig. 3(d)-(h) displays the HRTEM images of 40%WO₃/ g-C₃N₄. WO₃ is darker than g-C₃N₄, and WO₃ is marked with

the yellow circle. The lattice plane of 0.376 nm corresponds to the (002) plane of WO₃ (Fig. 3(h)).¹⁰ The EDS mapping images of 40%WO₃/g C₃N₄ (Fig. 3(i)) demonstrates the existence and the location of the C, N, O and W elements. These results further prove the successful preparation of 2D/2D WO₃/g C₃N₄.

The specific surface area and pore structure of the g-C₃N₄ and WO₃/g-C₃N₄ composites were studied by N₂ adsorptiondesorption isotherm (Fig. S1a, ESI†) using Micromeritics ASAP 2460. The pore size distribution diagram (Fig. S1b, ESI†) shows that the pore sizes of these six samples are mainly mesoporous. Among them, the pores of 40%WO₃/g-C₃N₄ are mainly distributed in the 1.5-16 nm range, and there are few mesopores smaller than 2 nm. 51 Table S1 (ESI†) summarizes the data for the specific surface area and pore volume. The specific surface areas of the WO₃/g-C₃N₄ composites are all smaller than that of pure $g-C_3N_4$, and $20\%WO_3/g-C_3N_4$ (11.88 m² g⁻¹) has the smallest specific surface area. The specific surface area sizes of 40% WO_3/g - C_3N_4 (14.87 m² g⁻¹) and 50% WO_3/g - C_3N_4 (14.90 m² g⁻¹) are similar. For the pore volume, the pure $g-C_3N_4$ (0.49 cm³ g⁻¹) is still the largest, and 20% WO₃/g-C₃N₄

Paper **Materials Advances**

 $(0.04 \text{ cm}^3 \text{ g}^{-1})$ is the smallest. The specific surface area and pore volume can affect the number of active sites, and thus affect the adsorption and reaction effect in the catalytic process. However, the specific surface area and pore volume are not necessarily better with larger sizes. It is necessary to synthesize other properties to obtain the final catalytic performance. Table S1 (ESI†) also shows the zeta potential of the g-C₃N₄ and WO₃/g-C₃N₄ composites in water.

Fig. 4(a) shows the results from investigating the optical properties of the g-C₃N₄, WO₃ and WO₃/g-C₃N₄ composites by ultraviolet and visible diffuse reflectance spectra (UV-Vis DRS, SHIMADZU UV-3600 Plus). Fig. 4(a) was converted into Fig. 4(b) using the Kubelka-Munk function, and the band gap (Eg) of the g-C₃N₄, WO₃ and WO₃/g-C₃N₄ composites was estimated. 41 The Eg values of pure g-C3N4 and pure WO3 are 2.48 eV and 2.41 eV, respectively. The similar $E_{\rm g}$ of these two pure substances leads to the similar Eg of the WO3/g-C3N4 composites, which is why the g-C₃N₄, WO₃ and WO₃/g-C₃N₄ composites are all yellow. The $\it E_{\rm g}$ of 40%WO $_{\rm 3}$ /g-C $_{\rm 3}$ N $_{\rm 4}$ and $50\%WO_3/g$ - C_3N_4 is 2.43 eV, which is the smallest E_g among the five WO₃/g-C₃N₄ composites and is more conducive to the absorption of visible light.

To further study the photogenerated carrier recombination probability of the g-C₃N₄ and WO₃/g-C₃N₄ composites, the photoluminescence (PL, HORIBA FluoroMax-4) spectra of the samples were tested. The weak PL peak intensity indicates the low recombination probability of the photogenerated carriers and high separation efficiency. 43,52 As shown in Fig. 4(c), the PL

peak intensity was ranked as $g-C_3N_4 > 30\%WO_3/g-C_3N_4 >$ $10\%WO_3/g-C_3N_4 > 20\%WO_3/g-C_3N_4 > 50\%WO_3/g-C_3N_4 >$ 40% WO₃/g-C₃N₄. The 40%WO₃/g-C₃N₄ photogenerated carrier recombination rate is the lowest in the above samples. Thus, the photogenerated e⁻-h⁺ separation efficiency of 40%WO₃/ g-C₃N₄ is the highest, which is conducive to improving its photocatalytic performance.

Electrochemical impedance spectroscopy (EIS, CHI660E Electrochemical Workstation) was used to further investigate the charge transfer capability of the g-C₃N₄, WO₃ and 40% WO₃/ g-C₃N₄ (Fig. 4(d)).⁴¹ A smaller arc radius on the EIS Nyquist diagram corresponds to a smaller charge transfer resistance on the working electrode surface. 41 In Fig. 4(d), the arc radius of 40% WO₃/g-C₃N₄ is smaller than that of g-C₃N₄ and WO₃, illustrating that 40% WO₃/g-C₃N₄ has better photogenerated electron-hole separation and transfer ability.

Photocatalytic degradation performance

Firstly, the photocatalyst and TC-HCl were mixed away from light for 30 min (t is -30 to 0 min in the corresponding Fig. 5(a)) to reach the adsorption-desorption equilibrium. The degradation efficiencies of the g-C₃N₄, WO₃ and WO₃/g-C₃N₄ composites as a photocatalyst for the antibiotic organic pollutant TC-HCl are shown in Fig. 5(a). The adsorption efficiency of the g-C₃N₄, WO₃ and WO₃/g-C₃N₄ composites for TC-HCl is about 7%. The adsorption rate of pure WO₃ to TC-HCl is slower than that of the g-C₃N₄ and WO₃/g-C₃N₄ composites, while the adsorption of bulk g-C₃N₄ to TC-HCl was almost zero. When t is 0 min, the visible light

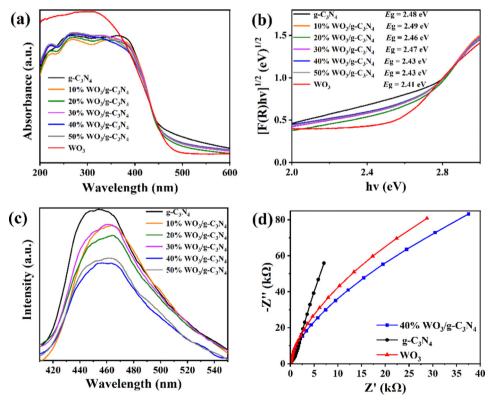


Fig. 4 (a) UV-vis DRS spectra, (b) E_q and (c) PL spectra of the g-C₃N₄, WO₃ and WO₃/g-C₃N₄ composites; (d) EIS of 40%WO₃/g-C₃N₄, g-C₃N₄ and WO₃.

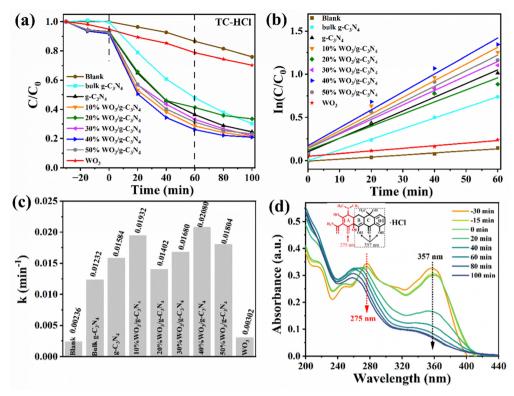


Fig. 5 (a) The photocatalytic degradation efficiency of TC-HCl by $g-C_3N_4$, WO_3 and $WO_3/g-C_3N_4$ composites under visible light, (b) corresponding first-order kinetic fitting curves and (c) corresponding UV-vis absorption spectra during the degradation of TC-HCl by $40\%WO_3/g-C_3N_4$.

source was turned on to start the photocatalytic reaction. "Blank" is the blank control without any photocatalyst. The self-degradation rate of TC-HCl is 24.1% after 100 min visible-light irradiation. The removal efficiency of TC-HCl by bulk g-C₃N₄, g-C₃N₄, WO₃, 10%WO₃/g-C₃N₄, 20%WO₃/g-C₃N₄, 30%WO₃/g-C₃N₄, 40%WO₃/g-C₃N₄ and 50%WO₃/g-C₃N₄ are 69.8%, 75.4%, 29.7%, 78.8%, 66.6%, 78.1%, 79.1% and 76.9%, respectively. It shows that $40\%WO_3/g$ -C₃N₄ has the best degradation effect on TC-HCl. The degradation rate of the WO₃/g-C₃N₄ composite became slow after the irradiation time t was 60 min, indicating that the maximum degradation efficiency was reached at 60 min. Therefore, t was 0–60 min for the first-order kinetic fitting (Fig. 5(b)). Fig. 5(a) shows the degradation process, and Fig. 5(b) shows the first-order kinetics fitting curve, which was calculated by eqn (2):

$$-\ln\left(\frac{C}{C_0}\right) = kt\tag{2}$$

where C_0 and C are the concentrations of the organic pollutants (mg L⁻¹, ppm) in water at the initial concentration and time t, respectively. The term k is the apparent rate constant (min⁻¹).


Fig. 5(c) is a histogram comparison of the apparent rate constant k. The k values of bulk g-C₃N₄, g-C₃N₄, WO₃, 10%WO₃/g-C₃N₄, 20%WO₃/g-C₃N₄, 30%WO₃/g-C₃N₄, 40%WO₃/g-C₃N₄ and 50%WO₃/g-C₃N₄ were 0.00236 min⁻¹, 0.01232 min⁻¹, 0.01584 min⁻¹, 0.00302 min⁻¹, 0.01932 min⁻¹, 0.01402 min⁻¹, 0.01680 min⁻¹, 0.02080 min⁻¹ and 0.01804 min⁻¹, respectively. Therefore, the introduction of the g-C₃N₄ nanosheets is greatly enhanced the catalytic effect of WO₃. Among them,

 $40\%WO_3/g$ - C_3N_4 had the best degradation efficiency, which was 1.69 times, 1.31 times and 6.89 times of bulk g- C_3N_4 , g- C_3N_4 and WO_3 , respectively.

Fig. 5(d) shows the UV-visible absorption spectrum during the adsorption and degradation of TC-HCl by 40%WO₃/g-C₃N₄. TC-HCl has two characteristic peaks at 275 nm and 357 nm, as shown in Fig. 5(d). It has been reported that the peak at 275 nm is associated with the aromatic ring A structure, including the enolic hydroxyl, amide and ketone groups. The peak at 357 nm is from aromatic rings B, C, and D, comprising the extended chromophores. 40%WO₃/g-C₃N₄ can simultaneously destroy the rings B, C, D, and A, but the destructive effect on A is relatively weak under visible light. The slight shift in the location of the characteristic peak may be caused by the slight change in pH during the removal process.

Fig. 6(a) shows the removal process of $40\%WO_3/g$ - C_3N_4 as a photocatalyst for three typical dyes with different charge properties, cationic dye MB, amphoteric dye RhB, and anionic dye MO. After 30 min dark adsorption process, 11.4% MB, 24.6% RhB and 1.8% MO can be removed. According to Table S1 (ESI†), $40\%WO_3/g$ - C_3N_4 was negatively charged in water, so the adsorption effect of the anionic dye MO was poor. When the light source was turned on, RhB was almost completely degraded after 20 min. After 100 min, the total removal rate of MB reached 91.4%, while that of MO was only 49.6%. Therefore, it proves that $40\%WO_3/g$ - C_3N_4 has a good removal effect on MB and RhB.

Fig. 6(b) shows the recycling experiments of $40\%WO_3/g$ -C₃N₄, where it can be seen that $40\%WO_3/g$ -C₃N₄ almost



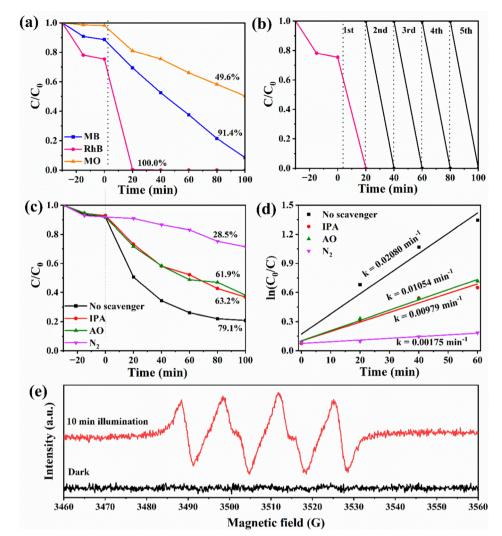


Fig. 6 (a) The removal process of MB, RhB and MO by 40%WO₃/g-C₃N₄. (b) Photodegradation cycle test of 40%WO₃/g-C₃N₄; (c) free radical capture experiments of the $0.3 \text{ g L}^{-1} 40\%\text{WO}_3/\text{g} - \text{C}_3\text{N}_4$ photocatalytic degradation of 10 mg L⁻¹ TC-HCl, and (d) their first-order kinetic fitting curves; and (e) EPR spectra of the DMPO- ${}^{\bullet}O_2^-$ adducts over $40\%WO_3/g$ - C_3N_4 under dark condition and with 10 min illumination in methanol.

maintained its original degradation efficiency of RhB after 5 cycles. Therefore, 40%WO₃/g-C₃N₄ possessed good photocatalytic stability for the potential application.

Photocatalytic degradation mechanism

It has been reported that the superoxide radical (${}^{\bullet}O_2^-$), hole (h⁺), and hydroxyl radical (*OH) are the main active species in photocatalytic oxidation reactions.⁵⁴ To study the photocatalytic degradation mechanism of the 40%WO₃/g-C₃N₄ photocatalyst, three trapping agents were applied to explore the active species in the photocatalytic reaction process. In this work, 1 mM ammonium oxalate (AO) was used to capture h⁺, and 1 mM isopropyl alcohol (IPA) was used to capture OH. N2 is used to remove O2 in the reaction system. It blocked the generation of •O₂ from the root. Therefore, N₂ can be used as the trapping agent of O2-.55 By adding different trapping agents in the reaction solution, the corresponding reactive species were removed. According to the change of photocatalytic efficiency,

the role of different active substances in the photocatalytic process can be determined. The device and process of the above capture experiment are the same as that of the photocatalytic performance test.

Fig. 6(c) shows the degradation process of 10 mg L^{-1} TC-HCl by 0.3 g L⁻¹ 40%WO₃/g-C₃N₄ when IPA, AO and N₂ were added to the reaction system. The removal rate decreased from 79.1% to 63.2%, 61.9% and 28.5%, respectively. It indicated that N₂ has the greatest impact on the removal rate. Therefore, O2was the main active species, while h⁺ and OH had similar effects as the minor active species. Fig. 6(d) shows the kinetic fitting curves for the photocatalytic process that is shown in Fig. 6(c). The first 60 min of the reaction process conforms to the first-order kinetic model. The apparent rate constants k decreased from 0.02080 min⁻¹ to 0.00979 min⁻¹, 0.01054 min^{-1} and 0.00175 min^{-1} , respectively (Fig. 6(d)). This verifies that the role of the active species in this process is ranked as ${}^{\bullet}O_2^- > h^+ \approx {}^{\bullet}OH$.

(a)

-1.01

-0.33

O₂ · O₂

O₃

O₄ · O₂

O₅

O₇

O₈

Fig. 7 The proposed mechanisms for the degradation of organic pollutants by $40\%WO_3/g-C_3N_4$ (a) Z-scheme heterojunction and (b) type-II heterojunction.

The valence band potential ($E_{\rm VB}$) and conduction band potential ($E_{\rm CB}$) of the semiconductor zero charge point (pH_{zpc}) can be estimated by eqn (3) and (4):^{56–60}

$$E_{\rm VB} = X - E_{\rm e} + 0.5 E_{\rm g}$$
 (3)

$$E_{\rm CB} = E_{\rm VB} - E_{\rm g} \tag{4}$$

where X is the geometric mean of the absolute electronegativity of the constituent atoms of the semiconductor, $E_{\rm e}$ is the energy of the free electron at the hydrogen scale, and $E_{\rm g}$ is the band gap. The X values of g-C₃N₄ and WO₃ were 4.73 eV and 6.49 eV, respectively.⁵⁴ According to eqn (3) and (4), it can be estimated that the $E_{\rm CB}$ values of g-C₃N₄ and WO₃ are -1.01 eV and 0.78 eV, respectively. The $E_{\rm VB}$ values of g-C₃N₄ and WO₃ are 1.47 eV and 3.19 eV, respectively.

Whether the ${}^{\bullet}O_2^-$ species are generated over 40% WO₃/g-C₃N₄ under light irradiation offers an important clue to determining the transfer route of the charge carriers. ${}^{\bullet}O_2^-$ was detected using electron paramagnetic resonance (EPR, Bruker EMXplus-6/1). In Fig. 6(e), the apparent ${}^{\bullet}O_2^-$ characteristic peaks can be observed in the EPR spectrum of 5,5-dimethyl-1-pyrroline N-oxide (DMPO)- ${}^{\bullet}O_2^-$ adduct over 40% WO₃/g-C₃N₄ after 10 min light illumination, demonstrating the generation of ${}^{\bullet}O_2^-$.

According to the results of the above capture experiments and EPR, two possible reaction mechanisms are proposed in Fig. 7. The electron (e⁻) on the CB of WO₃ and h⁺ on VB of g-C₃N₄ in the Z-scheme 40%WO₃/g-C₃N₄ heterojunction (Fig. 7(a)) are recombined. The CB of g-C₃N₄ is more negative than $O_2/^{\bullet}O_2^{-}$ (-0.33V vs. NHE), and the VB of WO₃ is more positive than H₂O/•OH (2.72V vs NHE), which allows •O₂ and OH to be produced. If g-C₃N₄ and WO₃ form a conventional type-II heterojunction (Fig. 7(b)), the CB of g-C₃N₄ will transfer e⁻ to the CB of WO₃, while the VB of WO₃ will transfer h⁺ to the VB of g-C₃N₄. However, in this case, the CB of WO₃ will be more positive than $O_2/^{\bullet}O_2^{-}$, so that the electrons on CB cannot reduce O2 to generate O2-.47 At the same time, the VB of g-C₃N₄ will be more negative than H₂O/•OH, so that the h⁺ in VB cannot oxidize H2O to generate OH.47 In conclusion, 40%WO₃/g-C₃N₄ is the Z-scheme heterojunction. This structure can improve the separation of the photogenerated e⁻ and h⁺, and enhance the redox ability of the photogenerated e- and h+ as well as the catalytic performance of the photocatalyst. 9-16

In addition, the comparison of almost all published 2D/2D *Z*-scheme WO_3/g - C_3N_4 heterojunction systems is shown in Table 1, which indicates that the facile synthetic 2D/2D *Z*-scheme WO_3/g - C_3N_4 heterojunctions in this work exhibit considerable photocatalytic performance in the environmental application and energy application without any cocatalyst. $^{9-16}$

 $\textbf{Table 1} \quad \text{Comparison of the 2D/2D Z-schemes of the WO_3/g-C_3N_4 heterojunction photocatalyst systems}$

Photocatalyst	Synthesis	Environmental application	Energy application	Ref.
WO ₃ ·H ₂ O/g-C ₃ N ₄	Ultrasonic-assisted self-assembly	95% RhB degradation in 80 min	_	9
WO ₃ /Ag/CN	Solvent evaporation and in situ calcination	96.2% RhB degradation in 40 min; \sim 90% TC degradation in 140 min	_	10
WO ₃ /CNT/g-C ₃ N ₄	Wet impregnation	92.3% MO degradation in 60 min	H ₂ production	11
Pt-g-C ₃ N ₄ /H-WO ₃	Post-annealing	_	H ₂ production	12
WO ₃ /RGO/H-g-C ₃ N ₄	Microwave-assisted hydrothermal method	\sim 90% TC-HCl degradation in 60 min		13
$WO_3/g-C_3N_4$	In situ construction	~100% RhB degradation in 40 min	_	14
$Pt-WO_3/g-C_3N_4$	Reverse microemulsion	_	H ₂ production	15
g-C ₃ N ₄ /Si-O/WO ₃	Wet chemical method	_	Aerobic alcohol oxidation	16
WO ₃ /g-C ₃ N ₄	Rapid calcination	79.1% TC-HCl, 91.4% MB and 49.6%	Nitrogen fixation	This
		MO degradation in 100 min, respectively; ~100% RhB degradation in 20 min	(NNR and NOR)	work

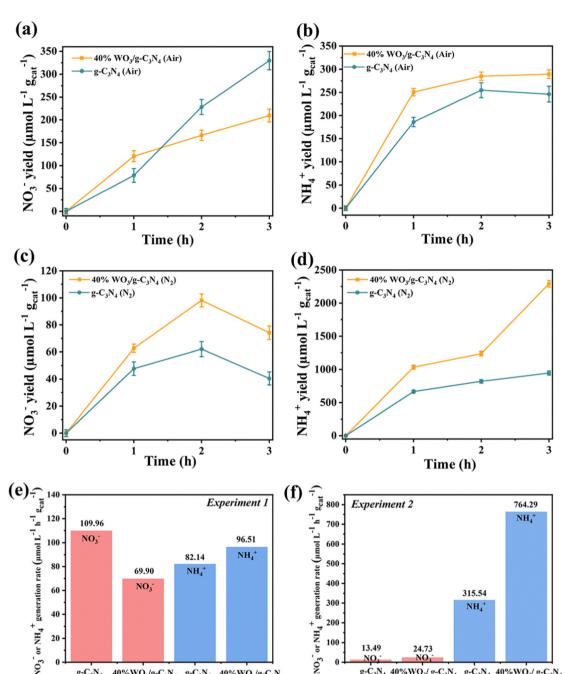


Fig. 8 Photocatalytic nitrogen fixation performance of $40\%WO_3/g-C_3N_4$ and $g-C_3N_4$: (a) the yield of NO_3^- in experiment 1, (b) the yield of NH_4^+ in Experiment 1, (c) the yield of NO₃⁻ in Experiment 2, and (d) the yield of NH₄⁺ in Experiment 2. Error bars represent the standard deviation of three independent experiments. (e) The 3 h average NO₃⁻ or NH₄⁺ generation rate in Experiment 1 of g-C₃N₄ and 40%WO₃/g-C₃N₄, and (f) the 3 h average NO₃⁻ or NH₄⁺ generation rate in Experiment 2 of g-C₃N₄ and 40%WO₃/g-C₃N₄.

40%WO₃/g-C₃N₄ g-C₃N₄ 40%WO₃/g-C₃N₄

Photocatalytic nitrogen fixation performance

Fig. 8(a), (b) and (e) show the generation of NO₃⁻ and NH₄⁺ in Experiment 1. As shown in Fig. 8(a), when the air was introduced into the aqueous suspension of 40%WO₃/g-C₃N₄ under Xenon lamp irradiation, the NO₃⁻ concentration increased with the increase of the reaction time. After 1 h, the NO₃ vield decreased, and the amount of the NO3- yield was lower than that of pure g-C₃N₄. As shown in Fig. 8(b), the yield of NH₄⁺ first increased for 1 h and then gradually stabilized. At the same

time, the yield was always higher than that of pure g-C₃N₄. Fig. 8(e) shows that the 3 h average NO₃⁻ yield of 40%WO₃/ g- C_3N_4 was 69.90 µmol L^{-1} h^{-1} g_{cat}^{-1} , and the 3 h average NH_4^+ yield was 96.51 µmol L^{-1} h^{-1} g_{cat}^{-1} . Unlike pure g- C_3N_4 , the yield of the nitrogen fixed product NO₃ in the N₂ disproportionation reaction of 40%WO₃/g-C₃N₄ was lower than that of NH₄⁺. The total nitrogen fixation efficiency of 40%WO₃/g-C₃N₄ was 166.41 μ mol L⁻¹ h⁻¹ g_{cat}⁻¹, which was lower than that of pure g-C₃N₄ (192.10 μ mol L⁻¹ h⁻¹ g_{cat}⁻¹). Therefore, the

g-C₃N₄ 40%WO₃/ g-C₃N₄ g-C₃N₄ 40%WO₃/ g-C₃N₄

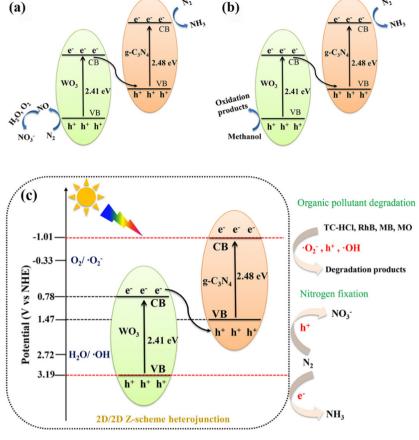


Fig. 9 The proposed photocatalytic nitrogen fixation mechanism of 40%WO₃/q-C₃N₄: (a) Experiment 1 and (b) Experiment 2; and (c) the proposed photocatalytic mechanism of the 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunctions in this work.

nitrogen disproportionation reaction efficiency of 40%WO₃/g-C₃N₄ in Experiment 1 was lower than that of pure g-C₃N₄ and the NRR accounted for a larger proportion in the disproportionation reaction.

The generation of NO₃⁻ and NH₄⁺ in Experiment 2 is shown in Fig. 8(c), (d) and (f). When N2 was introduced into a 20% methanol (as hole scavenger) aqueous suspension containing 40%WO₃/g-C₃N₄ under Xenon lamp irradiation, the NO₃ vield first increased and then decreased (Fig. 8(c)). In the 2 hours, a small amount of NO₃ was produced due to the removal of h⁺. After 2 hours, the e⁻ reduce NO₃⁻ and the NO₃⁻ yield decreased. For Fig. 8(d), the NH₄⁺ yield continued to increase. In addition, the NH₄⁺ yield of 40%WO₃/g-C₃N₄ was 2.37 times higher than that of pure g-C₃N₄. Fig. 8(f) shows that the 3 h average NO₃ yield of $40\%WO_3/g$ - C_3N_4 was $24.73~\mu mol~L^{-1}~h^{-1}~g_{cat}^{-1}$, and the 3 h average NH_4^+ yield was 764.29 µmol L^{-1} h⁻¹ g_{cat}^{-1} . NH_4^+ was the main nitrogen fixation product. The total nitrogen fixation efficiency of $40\%WO_3/g-C_3N_4$ (789.02 µmol L⁻¹ h⁻¹ g_{cat}⁻¹) was 2.40 times higher than that of the g-C₃N₄ nanosheets (329.03 $\mu mol~L^{-1}~h^{-1}~g_{cat}^{-1}$). Experiment 2 showed that 40% WO₃/g-C₃N₄ enhanced the NRR.

Photocatalytic nitrogen fixation mechanism

A photocatalytic nitrogen fixation mechanism based on the 40%WO₃/g-C₃N₄ Z-scheme heterojunction was proposed, as shown in Fig. 9(a) and (b). Under light irradiation, 40%WO₃/ g-C₃N₄ generated photogenerated electron-hole (e⁻-h⁺) pairs on VB. Then, e was transferred from VB to CB while leaving h on VB. In Experiment 1 (Fig. 9(a)), the photogenerated e⁻ on VB can be transferred to the surface via nitrogen vacancies. Then, e can reduce N2 (in the incoming air) to NH3. At the same time, the remaining photogenerated h⁺ in VB can oxidize N₂ (in the incoming air) to NO. Then, NO further reacts with O2 and H₂O to generate NO₃⁻. 31,34

In Experiment 1, N₂ underwent a disproportionation reaction to generate NH₄⁺ and NO₃⁻. It has been reported that the disproportionation reactions are energetically more favorable than the individual oxidation or reduction reactions.31 According to the law of charge conservation, the ratio of NO₃⁻ to NH₄⁺ generated in the N2 dismutation reaction should be 3:5.31 Nevertheless, the actual ratio of NO₃⁻ to NH₄⁺ is closer to 5:7. The slightly lower proportion of NH₄⁺ is due to the competition from the hydrogen evolution reaction (HER). In Experiment 1, 40%WO₃/g-C₃N₄ with the Z-scheme heterojunction was not more effective than pure g-C₃N₄. This is because g-C₃N₄ is beneficial to the adsorption and activation of N2, and the active ingredient of 40%WO3/g-C3N4 is mainly on the VB of WO₃. The adsorbed and activated N₂ on g-C₃N₄ is far from h⁺, which results in reduced NOR efficiency.

However, in Experiment 2 (Fig. 9(b)), the photogenerated h was consumed by the hole sacrifice agent, which highlighted

the advantage of the 40%WO₃/g-C₃N₄ Z-scheme heterojunction. A large amount of photogenerated e⁻ could reduce N₂ to NH₃ and improve the NRR reaction efficiency. Therefore, 40%WO₃/ g-C₃N₄ is suitable for photocatalytic nitrogen fixation, reducing N2 to ammonia. The reaction conditions of nitrogen fixation have a great influence on the reaction products of nitrogen fixation.

Conclusions

A series of 2D/2D Z-scheme WO₃/g-C₃N₄ heterojunctions were prepared by facile rapid calcination, and the degradation effect of different WO₃ ratios on the typical antibiotic organic contaminant TC-HCl was explored. The photocatalytic degradation effect of 40%WO₃/g-C₃N₄ is 1.69, 1.31 and 6.89 times higher than that of bulk g-C₃N₄, g-C₃N₄ and WO₃ nanosheets, respectively. The removal efficiency of RhB, MB and MO were 100%, 91.4% and 49.6%, respectively. The main reactive species of 40%WO₃/g-C₃N₄ in the degradation process was •O₂⁻. The 2D/ 2D Z-scheme WO₃/g-C₃N₄ can realize photocatalytic nitrogen fixation. With the presence of a hole sacrifice agent and N2 as the nitrogen source, the photocatalytic nitrogen fixation reaction of 40%WO₃/g-C₃N₄ was dominated by NRR, and the almost all product was NH₄ $^+$ (764.29 $\mu mol~L^{-1}~h^{-1}~g_{cat}^{}$). The total nitrogen fixation efficiency was 2.40 times higher than that of pure g-C₃N₄. The results prove that the 2D/2D Z-scheme heterojunction enhanced the photogenerated electron-hole separation and transfer ability, which is very effective in both photocatalytic degradation and photocatalytic nitrogen fixation application scenarios (Fig. 9(c)). This work provides a reference for understanding the 2D/2D Z-scheme heterojunctions, photocatalytic NRR and NOR reactions, and the photocatalytic degradation process of antibiotics and organic pollutants with different charge properties.

Author contributions

Yasi Li contributed to the experimental design, investigation, validation, and writing of the original draft. Junkai Wang performed the conceptualization, methodology, investigation, visualization, and funding acquisition.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was funded by the Special Program for Science Research Foundation of the Higher Education Institutions of Guangdong Providence (grant no. 2020ZDZX2052), and the Shantou University Scientific Research Foundation for Talents (grant no. NTF22004).

References

- 1 J. Bai, R. Shen, Z. Jiang, P. Zhang, Y. Li and X. Li, Chin. J. Catal., 2022, 43, 359-369.
- 2 Y. Hu, X. Li, W. Wang, F. Deng, L. Han, X. Gao, Z. Feng, Z. Chen, J. Huang, F. Zeng and F. Dong, Chin. J. Struct. Chem., 2022, 41, 2206069.
- 3 G. M. Li, B. Wang and R. Wang, Chin. J. Struct. Chem., 2020, 39, 1675-1688.
- 4 Z. Jin, Y. Li and X. Hao, Acta Phys.-Chim. Sin., 2021, 37, 1912033.
- 5 X. Li, B. Wang, W. Yin, J. Di, J. Xia, W. Zhu and H. Li, Acta Phys.-Chim. Sin., 2020, 36, 17401.
- 6 L. Huang, H. Xu, Y. Li, H. Li, X. Cheng, J. Xia, Y. Xu and G. Cai, Dalton Trans., 2013, 42, 8606-8616.
- 7 Y. Y. Zhou, J. X. Zhang and D. F. Wu, ChemistrySelect, 2023, 8, e202301237.
- 8 K. He, J. Xie, X. Luo, J. Wen, S. Ma, X. Li, Y. Fang and X. Zhang, Chin. I. Catal., 2017, 38, 240-252.
- 9 L. Li, D. Jiang, X. Wu, X. Sun, X. Qu, L. Shi and F. Du, J. Mater. Sci., 2020, 55, 4238-4250.
- 10 J. Chen, X. Xiao, Y. Wang and Z. Ye, Appl. Surf. Sci., 2019, 467-468, 1000-1010.
- 11 U. Bharagav, N. R. Reddy, V. N. K. Rao, P. Ravi, M. Sathish, D. Rangappa, K. Prathap, C. S. Chakra, M. V. Shankar, L. Appels, T. M. Aminabhavi, R. R. Kakarla and M. M. Kumari, Chemosphere, 2023, 311, 137030.
- 12 D. Liu, S. Zhang, J. Wang, T. Peng and R. Li, ACS Appl. Mater. Interfaces, 2019, 11, 27913-27923.
- 13 Y. Bao, H. Guo, L. Jiang, Z. Liu, J. Qu, C. Zhang, X. Jia and K. Chen, Appl. Surf. Sci., 2019, 496, 143639.
- 14 H. Zhang, Z. Cai, W. Xu, M. Huang and X. Liu, New J. Chem., 2019, 43, 17416.
- 15 S. Tang, Y. Ma, H. Wang, Y. Liang, X. Xu, D. Zhang, B. Cao, Q. Wang and W. Li, *ChemSusChem*, 2023, **16**, e202202184.
- 16 L. Sun, B. Li, X. Chu, N. Sun, Y. Qu, X. Zhang, I. Khan, L. Bai and L. Jing, ACS Sustainable Chem. Eng., 2019, 7, 9916-9927.
- 17 Z. B. Wu, X. Z. Yuan, J. Zhang, H. Wang, L. B. Jiang and G. M. Zeng, ChemCatChem, 2017, 9, 41-64.
- 18 E. Forgacs, T. Cserhati and G. Oros, Environ. Int., 2004, 30, 953-971.
- 19 X. R. Yang, Z. Chen, W. Zhao, C. X. Liu, X. X. Qian, M. Zhang, G. Y. Wei, E. Khan, Y. H. Ng and Y. S. Ok, Chem. Eng. J., 2021, 405, 126806.
- 20 H. Yang, Z. C. Zhao, Y. P. Yang, Z. Zhang, W. Chen, R. Q. Yan, Y. X. Jin and J. Zhang, Sep. Purif. Technol., 2022, 300, 121846.
- 21 Y. X. Li, M. Fu, R. Q. Wang, S. W. Wu and X. M. Tan, Chem. Eng. J., 2022, 444, 136567.
- 22 J. Guo, T. T. Liu, H. Peng and X. G. Zheng, Int. J. Mol. Sci., 2022, 23, 9343.
- 23 F. D. Wu, J. C. Chen and J. P. Hu, J. Environ. Chem. Eng., 2022, 10, 107117.
- 24 S. Krobthong, T. Rungsawang and S. Wongrerkdee, Toxics, 2023, 11, 266.
- 25 G. H. Dong, W. K. Ho and C. Y. Wang, J. Mater. Chem. A, 2015, 3, 23435-23441.

Materials Advances

- 27 P. F. Xia, X. C. Pan, S. L. Jiang, J. G. Yu, B. W. He, P. M. Ismail, W. Bai, J. J. Yang, L. Yang, H. H. Zhang, M. Cheng, H. Y. Li, Q. Zhang, C. Xiao and Y. Xie, Adv. Mater., 2022, 34, 2200563.
- 28 M. Cheng, C. Xiao and Y. Xie, J. Mater. Chem. A, 2019, 7, 19616-19633.
- 29 N. Cherkasov, A. O. Ibhadon and P. Fitzpatrick, Chem. Eng. Process., 2015, 90, 24-33.
- 30 X. Z. Chen, N. Li, Z. Z. Kong, W. J. Ong and X. J. Zhao, Mater. Horiz., 2018, 5, 9-27.
- 31 W. J. Ren, Z. W. Mei, S. S. Zheng, S. N. Li, Y. M. Zhu, J. X. Zheng, Y. Lin, H. B. Chen, M. Gu and F. Pan, Research, 2020, 2020, 3750314.
- 32 Y. T. Wang, Y. F. Yu, R. R. Jia, C. Zhang and B. Zhang, Natl. Sci. Rev., 2019, 6, 730-738.
- 33 X. B. Chen, L. Liu, P. Y. Yu and S. S. Mao, Science, 2011, 331, 746-750.
- 34 H. Tong, S. X. Ouyang, Y. P. Bi, N. Umezawa, M. Oshikiri and J. H. Ye, Adv. Mater., 2012, 24, 229-251.
- 35 X. C. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, Nat. Mater., 2009, 8, 76-80.
- 36 W. J. Ong, L. L. Tan, Y. H. Ng, S. T. Yong and S. P. Chai, Chem. Rev., 2016, 116, 7159-7329.
- 37 R. B. Xu, M. H. Su, Y. H. Liu, Z. B. Chen, C. Ji, M. L. Yang, X. Y. Chang and D. Y. Chen, J. Cleaner Prod., 2020, 242, 118366.
- 38 Y. S. Li, M. R. Ti, Z. Q. Li, Y. Zhang, L. Wu and Y. J. He, J. Mater. Sci.: Mater. Electron., 2021, 32, 2268-2282.
- 39 T. T. Xiao, Z. Tang, Y. Yang, L. Q. Tang, Y. Zhou and Z. G. Zou, Appl. Catal., B, 2018, 220, 417-428.
- 40 Y. J. Xue, Y. C. Guo, Z. G. Liang, H. Z. Cui and J. Tian, J. Colloid Interface Sci., 2019, 556, 206-213.
- 41 Y. Li, M. Ti, D. Zhao, Y. Zhang, L. Wu and Y. He, J. Alloys Compd., 2021, 870, 159298.
- 42 Y. T. Xiao, G. H. Tian, W. Li, Y. Xie, B. J. Jiang, C. G. Tian, D. Y. Zhao and H. G. Fu, J. Am. Chem. Soc., 2019, 141, 2508-2515.

- 43 Y. J. Xue, X. K. Kong, Y. C. Guo, Z. Q. Liang, H. Z. Cui and J. Tian, J. Materiomics, 2020, 6, 128-137.
- 44 X. Chen, J. Y. Li, Z. R. Tang and Y. J. Xu, Catal. Sci. Technol., 2020, 10, 6098-6110.
- 45 V. Luxmi and A. Kumar, Mater. Sci. Semicond. Process., 2019, 104, 104690.
- 46 S. Prabhu, S. Manikumar, L. Cindrella and O. J. Kwon, Mater. Sci. Semicond. Process., 2018, 74, 136-146.
- 47 W. Yu, J. Chen, T. Shang, L. Chen, L. Gu and T. Peng, Appl. Catal., B, 2017, 219, 693-704.
- 48 J. Meng, X. Wang, Y. Liu, M. Ren, X. Zhang, X. Ding, Y. Guo and Y. Yang, Chem. Eng. J., 2021, 403, 126354.
- 49 H. Yu, R. Shi, Y. Zhao, T. Bian, Y. Zhao, C. Zhou, G. I. N. Waterhouse, L. Z. Wu, C. H. Tung and T. Zhang, Adv. Mater., 2017, 29, 1605148.
- 50 J. Fu, Q. Xu, J. Low, C. Jiang and J. Yu, Appl. Catal., B, 2019, 243, 556-565.
- 51 Y. Wang, X. Di, X. Wu and X. Li, J. Alloys Compd., 2020, 846, 156215.
- 52 W. Ho, Z. Zhang, W. Lin, S. Huang, X. Zhang, X. Wang and Y. Huang, ACS Appl. Mater. Interfaces, 2015, 7, 5497-5505.
- 53 Y. Quan, M. Liu, H. Wu, X. Tian, L. Dou and Z. Wang, Appl. Surf. Sci., 2024, 642, 158601.
- 54 S. Chen, Y. Hu, S. Meng and X. Fu, Appl. Catal., B, 2014, 150, 564-573.
- 55 X. Liu, A. Jin, Y. Jia, T. Xia, C. Deng, M. Zhu, C. Chen and X. Chen, Appl. Surf. Sci., 2017, 405, 359-371.
- 56 M. Chatterjee, M. Mondal, T. Sukul, K. Ghosh and S. K. Pradhan, J. Ind. Eng. Chem., 2023, 127, 390-405.
- 57 S. Zwane, D. S. Dlamini, B. B. Mamba and A. T. Kuvarega, Inorg. Chem. Commun., 2023, 151, 110637.
- 58 M. Lv, H. Wang and H. Shi, Colloids Surf., A, 2023, 679, 132579.
- 59 C. Mrabet, R. Jaballah, N. Mahdhi, A. Boukhachem and M. Amlouk, J. Alloys Compd., 2023, 968, 172252.
- 60 K. Li, J. Zhu, W. Zhou, L. Sun and S. Tian, J. Alloys Compd., 2023, 968, 171955.
- 61 L. Zhang, J. Qiu, G. Xia, D. Dai, X. Zhong and J. Yao, J. Mater. Sci. Technol., 2023, 138, 214-220.
- 62 X. Mo, X. Zhang, B. Lin, C. Ning, M. Li, H. Liao, Z. Chen and X. Wang, J. Mater. Sci. Technol., 2023, 145, 174-184.