



Cite this: *React. Chem. Eng.*, 2025, 10, 294

Received 19th September 2024,
Accepted 3rd December 2024

DOI: 10.1039/d4re00449c

rsc.li/reaction-engineering



Metallic sealants increase flux and change selectivity in supported molten-salt membranes

Liam A. McNeil, Guannan Chen, Wenting Hu,  Evangelos I. Papaioannou, 
 Ian S. Metcalfe  and Greg A. Mutch *

Metallic sealants are widely used with high-temperature membranes. Here we show that their use in supported molten-salt membranes results in order-of-magnitude differences in CO₂ flux and introduces O₂ co-permeation. The ‘short-circuiting’ effect they introduce has important implications for the design of future experiments, and the interpretation of past work.

A key but often overlooked component of membrane modules and reactors is the sealant used to ensure that the fluid streams on the two sides of a membrane do not mix. However, to achieve this, the sealant must be in contact with both streams. Thus, the role of the sealant on flux and selectivity through a membrane should be considered. In high-temperature ceramic membranes, metallic sealants are frequently employed in the hot zone. Their use can, in principle, introduce poorly defined, transmembrane electronic conductivity.

Supported molten-salt membranes comprise a porous solid support, typically a metal oxide or metal, with molten salts infiltrated into the pore space *via* capillarity.¹ Current literature suggests that they selectively permeate CO₂ when they comprise molten carbonates supported in an oxygen-ion conductor *via* reaction 1, and that they co-permeate CO₂ and O₂ when an electronic conductor is employed *via* reaction 2.



There are, however, contradictory results in the literature, which suggests there is unappreciated mechanistic nuance. The wide variety of support geometries and materials, salt compositions, and sealants used may be responsible for some of the contradictions as they introduce the potential for the

superposition of different mechanisms in a single membrane (*e.g.*, reaction 2 introduced *via* the use of a metallic sealant to a membrane otherwise expected to follow reaction 1).

The lack of consensus around the CO₂ permeation mechanism in arguably the simplest class of supported molten-carbonate membrane, *i.e.*, molten carbonates supported in a nominally inert material (*e.g.*, Al₂O₃), best highlights this issue. A variety of oxide-, hydroxide-, bicarbonate-, and carbonate-like species are posited as being stable in molten carbonates,^{2–6} which would in theory allow CO₂ transport *via* a mechanism similar to reaction 1 in the molten phase alone. There have also been suggestions that electronic conductivity in molten carbonates (rather than in the support as in reaction 2) due to the formation of dissolved metal/cation pairs is responsible.⁷ Finally, the transport of neutral, dissolved CO₂ (a solution-diffusion mechanism) is also possible, although comparing the physical and chemical (reactive) solubilities of CO₂ in molten carbonates suggests such a mechanism likely does not contribute significantly.^{1,8}

Despite inert supports providing lower CO₂ fluxes than oxide ion- and electron-conducting supports, they provide very useful permeation and mechanistic data as they simplify the membrane by restricting permeation to the molten-carbonate salt alone.^{9–13} Moreover, with their low intrinsic CO₂ fluxes, modifications to the membrane leading to increased fluxes can be easier to measure. For example, in our previous work, the growth of an electronically-conductive, transmembrane Ag structure within an Al₂O₃ support increased CO₂ and O₂ flux compared to the Al₂O₃ support alone.¹² This was achieved by doping the molten-carbonate salt with Ag. Selectivity was also influenced, whereby O₂ co-permeation (with CO₂) occurred only in the membrane with Ag. Work on cermet-supported, molten-salt membranes has also shown that the incorporation of Ag into the membrane support provides high CO₂ fluxes.^{14,15}

Our previous work on Ag doping encouraged us to consider the potential impact of metallic sealants, as these are

Materials, Concepts, and Reaction Engineering (MatCoRE) Group, School of Engineering, Newcastle University, Newcastle upon Tyne, NE1 7RU, UK.
 E-mail: greg.mutch@newcastle.ac.uk



frequently employed with supported molten-salt membranes due to the high operating temperatures of these membranes (~ 400 – 1000 °C). This has included Ag,^{14–31} and Au sealants,^{32,33} despite suggestions (but no experimental proof) that they might introduce poorly-defined, transmembrane electronic conductivity.^{34,35} An alternative approach is to avoid sealing in the hot zone, employing a cold-zone seal instead. However, at the lab-scale this has rarely been employed, as it can involve preparing larger and more complex dense membrane supports, followed by the introduction of porosity using *e.g.*, micro-scale subtractive manufacturing.^{12,13,36} Overall, this results in a much more expensive membrane and one which may not be suitable for real applications. However, as the sealant remains in the cold zone, the quality of the seal can be greatly improved which is important for interpreting permeation data and deriving mechanism.

Here we show that the use of metallic sealants with supported molten-salt membranes results in changes in flux and selectivity from feed-gas mixtures of importance for carbon dioxide separation. The use of a cold-zone-sealed Al_2O_3 support restricted permeation to the molten carbonate alone and demonstrated that molten carbonates selectively permeate only CO_2 from both CO_2/N_2 and $\text{CO}_2/\text{O}_2/\text{N}_2$ feed-gas mixtures. The use of both Au and Ag sealants in the hot zone with Al_2O_3 supports resulted in CO_2 and O_2 co-permeation from a $\text{CO}_2/\text{O}_2/\text{N}_2$ feed-gas mixture, indicating a clear and significant impact on selectivity due to the transmembrane electronic conductivity introduced by the sealant. Furthermore, the metallic sealants increased CO_2 flux significantly ($\sim 1 \times 10^{-2}$ ml min⁻¹ cm⁻² with Au, and $\sim 16 \times 10^{-2}$ ml min⁻¹ cm⁻² with Ag). If supported molten-salt membranes are to progress towards scale-up, robust permeation and mechanistic data will be required; our results clearly demonstrate that consideration must be given to the sealants used.

Experimental

Membrane fabrication

Two membrane support geometries were employed: pressed pellets with a random porous architecture which required a hot-zone seal (Au or Ag), and tubular membranes with laser-drilled pores which required a cold-zone seal (O-ring and vacuum grease). These are hereafter referred to by the nature of the sealant, *i.e.*, as hot- or cold-zone-sealed supports (before carbonate infiltration) and hot- or cold-zone-sealed membranes (following carbonate infiltration).

To produce the hot-zone-sealed supports, Al_2O_3 powder (Alpha Aesar, ACS, >99.5%) was mixed with a 10 wt% PVA binder in a 1 ml binder:1.5 g Al_2O_3 ratio. 1 g of this mixture was uniaxially pressed at 3 tonnes to form ~ 1.75 mm thick, ~ 20 mm diameter pellets using a hydraulic press. Pellets were sintered at 1200 °C for 5 h at a ramp rate of 2 °C min⁻¹, before being sealed to Al_2O_3 tubes with two open ends (~ 200 mm length, 12 mm outer diameter, 9 mm inner diameter) using commercial hot-zone sealants (Au and Ag pastes from Fuel

Cell Materials). The metallic pastes were applied to the rim of the Al_2O_3 tube, before the tubes were pressed on to the pellets from above. Further metallic paste was applied around the external circumference of the Al_2O_3 tube, and the entire assembly was held in place with a clamp for ~ 1 h at room temperature for initial adhesion. Metallic sealants were set at 850 °C in air, employing a heating rate of 1 °C min⁻¹. After holding the support and sealant at 850 °C for 1 h, they were cooled at a rate of 1 °C min⁻¹ to room temperature.

For the cold-zone-sealed supports, Al_2O_3 tubes (~ 200 mm length, 20 mm outer diameter, 15 mm inner diameter) with one closed end of thickness ~ 500 μm were laser drilled to form ~ 2000 parallel pores within the central ~ 15 mm diameter of the closed end. These laser-drilled tubes have been described in detail previously.^{12,13,36} They do not require a hot-zone sealant.

To prepare the carbonate phase of the membranes, individual lithium, sodium, and potassium carbonate powders (Alpha Aesar, ACS, >99.5%) were dried at ~ 300 °C for ~ 24 h in air, before being mixed in a $\sim 43.5:31.5:25$ (Li:Na:K) mol% ratio.

Membrane reactor

To seal both the hot- and cold-zone-sealed supports to the membrane reactor, a rubber O-ring and high-quality vacuum greases were applied to the open end of the Al_2O_3 tubes (noting that the hot-zone-sealed supports have the additional metallic sealant between the pressed pellet and Al_2O_3 tube). The open end of the tubes was situated in the base of the membrane reactor. The membrane reactor has been described in detail previously.^{12,13,36}

Infiltration of supports was achieved by pressing the eutectic carbonate mixture into pellets which were placed on the surface of the membrane supports (~ 20 and 15 mm diameter pellets of mass ~ 0.6 and 0.06 g were employed for the hot- and cold-zone-sealed supports respectively, *i.e.*, they were of the same diameter as the porous areas of the supports and of a mass required to occupy the volume of the pores). The supports with carbonate pellets were enclosed within a quartz tube and heated to 450 °C at 1 °C min⁻¹ under a flow of 50 mol% CO_2 in N_2 supplied to both feed and permeate sides. They were held at 450 °C for ~ 1 h to permit infiltration of the molten carbonate ($T_m \approx 400$ °C), before the reactor was heated to the experimental temperature (650 °C) at 1 °C min⁻¹. At the experimental temperature the permeate-side gas was switched to Ar and the feed gas was either 50 mol% CO_2 in N_2 or 50 mol% CO_2 , 25 mol% O_2 in N_2 . Detection of N_2 at the permeate-side outlet above any pre-existing background level indicated a leaking membrane, at which point the experiment was abandoned. Similarly, CO_2 or O_2 permeation was assumed when signals exceeded their background level in Ar. All flow rates were 50 ml min⁻¹, controlled by Brooks Smart II mass flow controllers, and measured at NTP.



CO₂ and O₂ flux measurement

During permeation, the permeate-side outlet gas composition was monitored using a quadrupole mass spectrometer (Hidden Analytical QGA). The mass spectrometer was calibrated using Ar (background), and ~0.04 and 1 mol% CO₂ mixtures. Mole fractions of permeated gases were converted to volumetric flux, J_i (ml min⁻¹ cm⁻²) using eqn (1),

$$J_i = y_i \times Q \times 1/A \quad (1)$$

where y_i is the mole fraction of species i in the gas phase, Q is the volumetric flow rate of the permeate-side gas in ml min⁻¹, and A is the permeate-side area in cm².¹¹ The area used for the hot-zone-sealed membranes was ~0.4 cm² (based on the ~7 mm inner diameter remaining after sealant spreading). For the cold-zone-sealed membranes, the area used was ~1.8 cm² (based on the ~15 mm inner diameter/laser-drilled area).

Membrane characterisation

Scanning electron microscopy (SEM), performed using a Tescan Vega 3LMU instrument, was used to analyse a membrane following gas permeation measurements. Digital images were collected using a digital camera and digital microscope.

Results and discussion

Fig. 1 demonstrates that the cold-zone-sealed support and membrane possessed an exceptionally high-quality seal. First, a cold-zone-sealed support without laser-drilled pores was supplied with a 50 ml min⁻¹ Ar sweep gas to determine the background mole fractions of N₂ and O₂ present due to *e.g.*, air leaks into the membrane reactor, mass spectrometer, and tubing/fittings used to connect the apparatus, and due to impurities in the Ar. N₂ was present at ~275 ppm and O₂ at ~125 ppm in the outlet of the sweep gas, suggesting that

there were minimal leaks into the apparatus (Fig. 1b). Based on the ~2000:1 (mole fraction in the air:mole fraction in the reactor) ratio for N₂ and O₂, this would suggest that the mole fraction of CO₂ in the reactor as a result of air leaks would be on the order of 0.1 ppm.

Subsequently, the cold-zone-sealed membrane was supplied with a 50 mol% CO₂, 25 mol% O₂ in N₂ feed gas and an Ar sweep gas at 650 °C. The lack of any significant change in the level of N₂ indicated that despite the support having been laser drilled and infiltrated with molten carbonates, there were no measurable transmembrane leaks (N₂ is not expected to permeate a molten-carbonate membrane) (Fig. 1c). The presence of CO₂ at ~20 ppm (two orders of magnitude higher mole fraction than that expected due to air leaks into the reactor) in the permeate-side outlet is due to selective permeation through the molten-carbonate salt (discussed below). We note that if the N₂ and O₂ background in Fig. 1b was subtracted from the permeation experiment in Fig. 1c, their mole fractions would become ~0 ppm. This background subtraction methodology was applied in all experiments reported hereafter. Clearly, there is no measurable O₂ flux, however, using the CO₂ mole fraction from Fig. 1c, a low CO₂ flux ($<0.1 \times 10^{-3}$ ml min⁻¹ cm⁻²) can be calculated. Together, these results suggest that the molten-carbonate phase does not possess sufficient electronic conductivity to contribute significantly to CO₂ permeation *via* a reaction like reaction 2, contrary to some previous proposals.⁷

As discussed above, we suspected that metallic sealants may introduce transmembrane electronic conductivity. Indeed, when hot-zone-sealed membranes were exposed to the same conditions (feed gases, sweep gas, and temperature) used with the cold-zone-sealed membrane, the results were quite different (Fig. 2). With a 50 mol% CO₂, 25 mol% O₂ in N₂ feed gas ((1) and (3) in Fig. 2b), CO₂ and O₂ co-permeated the membrane sealed with Au, with a CO₂ flux of up to $\sim 1 \times 10^{-2}$ ml min⁻¹ cm⁻². We suggest that the introduction of transmembrane electronic conductivity to the membrane

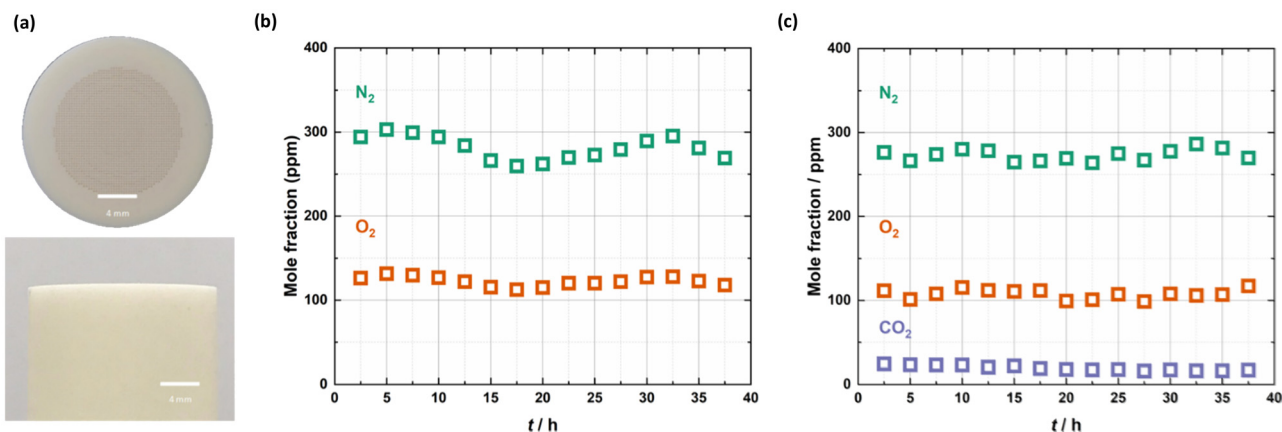


Fig. 1 Leak testing with the cold-zone-sealed support and CO₂ permeation in the cold-zone-sealed membrane. (a) Images of a cold-zone-sealed membrane. (b) Mole fraction of N₂ and O₂ in the Ar sweep-gas outlet, with a cold-zone sealed support without laser-drilled pores. (c) Mole fraction of N₂, O₂ and CO₂ in the Ar sweep-gas outlet during a permeation experiment at 650 °C with a 50 mol% CO₂, 25 mol% O₂ in N₂ feed gas.



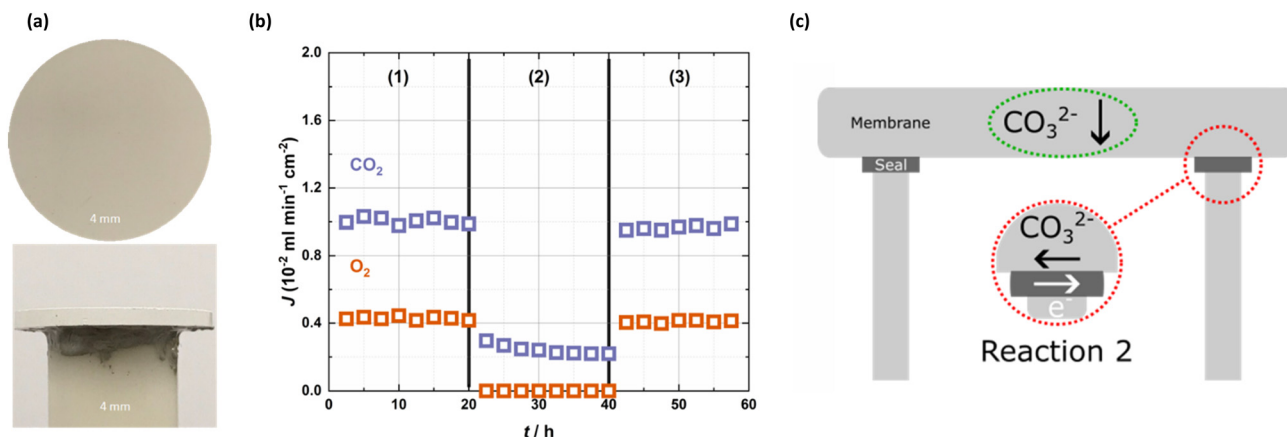


Fig. 2 Short-circuiting due to the Au sealant. (a) Images of a hot-zone-sealed membrane. (b) CO_2 and O_2 fluxes as a function of feed gas at 650 °C in the Au, hot-zone-sealed membrane. An Ar sweep gas was used across all sections, with feed gas varying: (1) 50% CO_2 , 25% O_2 in N_2 , (2) 50% CO_2 in N_2 and (3) 50% CO_2 , 25% O_2 in N_2 . (c) Schematic of the short-circuiting effect due to metallic sealants, where reaction 2 is introduced via the metallic sealant.

facilitated the co-permeation of CO_2 and O_2 via reaction 2 by 'short-circuiting' the membrane (Fig. 2c).^{34,35} Moreover, the $\text{CO}_2:\text{O}_2$ flux ratio in (1) and (3) of Fig. 2 is $\sim 2.5:1$, but if the CO_2 flux in (2) (note that the O_2 flux is zero), where a 50 mol% CO_2 in N_2 feed gas was employed are subtracted, then the ratio is $\sim 2:1$, consistent with reaction 2. This suggests that in (1) and (3), there is a superposition of reaction 2 (on top of the reaction responsible for permeation in (2)) due to the presence of O_2 and transmembrane electronic conductivity via the Au sealant. Overall, Fig. 2 clearly demonstrates that the Au sealant 'switches on' selectivity for O_2 , and that when reaction 2 can occur due to the presence of O_2 in the feed gas, CO_2 flux is increased by $\sim 400\%$ (comparing (1) and (3) to (2) in Fig. 2).

The impact of metallic sealants was further evidenced by using the Ag sealant in place of the Au sealant (Fig. 3). In this case, again O_2 co-permeation was observed with a 50 mol%

CO_2 , 25 mol% O_2 in N_2 feed gas, but this time with significant migration of the Ag sealant across the surface of, and into the bulk, of the membrane (Fig. 3b–d). Although not shown here, migration of Au was not observed (this, and the mechanism of Ag migration is discussed in our previous work).¹² Notably, the use of the Ag sealant resulted in the highest CO_2 fluxes in this work ($\sim 16 \times 10^{-2} \text{ ml min}^{-1} \text{ cm}^{-2}$, an order of magnitude higher than with the Au sealant under identical conditions). The flux remained at this level for >200 h. Also, we note the $\text{CO}_2:\text{O}_2$ flux ratio of $\sim 2:1$, in line with reaction 2. In this case, with such high CO_2 and O_2 fluxes, the small contribution of any other permeation mechanism is concealed.

The very significant impact that the Ag sealant had on flux and selectivity is particularly concerning due to the aforementioned widespread use of Ag sealants in the supported molten-salt membrane literature.^{14–31} Table 1 shows that a variety of Ag sealant forms (pastes, gaskets *etc.*)

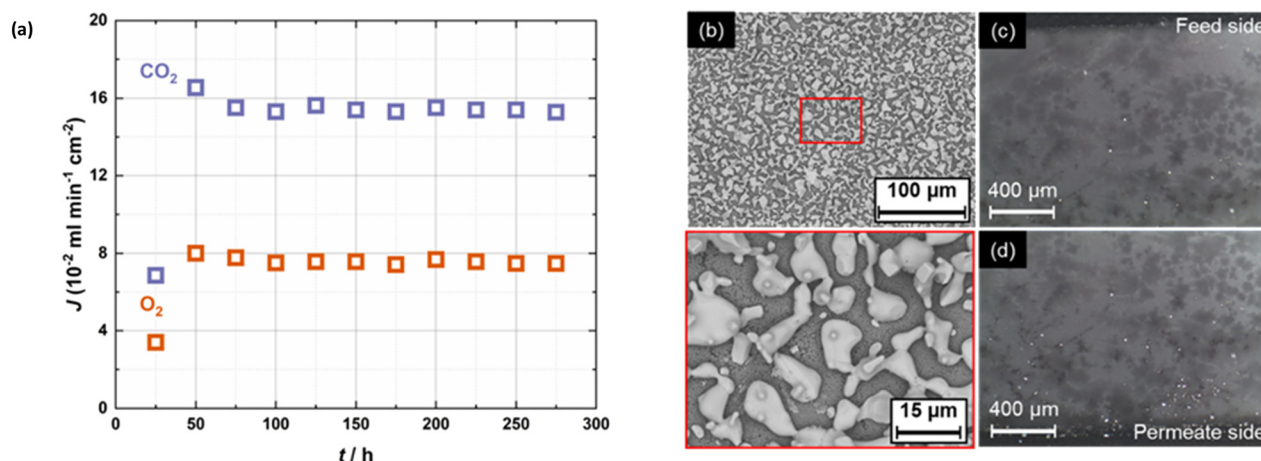


Fig. 3 Significant short-circuiting due to the Ag sealant. (a) CO_2 and O_2 fluxes at 650 °C in the Ag, hot-zone-sealed membrane. An Ar sweep gas was used, with feed gas 50% CO_2 , 25% O_2 in N_2 . (b) SEM images of the permeate side after use showing significant migration of the Ag sealant over the surface. (c and d) Images of the feed- and permeate-side cross-sections following the permeation experiment, showing migration of the Ag sealant into the bulk of the membrane.

Table 1 Sealant materials and forms employed in the supported molten-salt membrane literature

Sealant material	Sealant form	Ref.
Au	Paste	32, 33
Ag	Paste	18–24, 27–30
	Gasket	14, 15, 31
	Not described	16, 17, 25, 26
Graphite	Gasket	6, 37
	Not described	17, 38–42

have been employed at the laboratory scale. This variety likely means that the effects we discuss (changes in flux and selectivity) will differ quantitatively between studies. Moreover, the sealant quantity and sealing area in laboratory-scale studies is relatively large when compared to membrane geometries used in industrial applications. Thus, one might expect quantitative differences here also. However, it is very important to note that this could result in performance (*e.g.*, flux) at the laboratory scale that cannot be realised upon scale up.

Finally, we note that whilst we have studied the impact of metallic seals, graphite seals (which have an electronic conductivity approximately one order of magnitude lower than metals) are also used with supported molten-salt membranes, and therefore may unintentionally introduce contributions to permeation *via* reaction 2 also.^{6,17,37–42} It is possible that oxide-ion conducting sealants may introduce reaction 1 contributions similarly.

Conclusions

The influence that sealants have on flux and selectivity in membranes at the lab-scale should be carefully investigated as efforts towards the scale-up of membrane modules and reactors may otherwise encounter unforeseen difficulties. Here we have shown that metallic hot-zone sealants ‘switch on’ O₂ selectivity in supported molten-salt membranes. This conclusion was supported by comparison to a cold-zone-sealed membrane, which showed no measurable O₂ permeation under the same conditions. Furthermore, the metallic sealants significantly increased CO₂ flux, with an order-of-magnitude difference observed between Au and Ag sealants. Going forwards, mechanistic interpretation, and comparisons of the performance between different membranes should consider the significant impact that sealant choice can have.

Data availability

Data for this article are available at data.ncl at <https://doi.org/10.25405/data.ncl.27045505>.

Author contributions

Funding acquisition (EIP, ISM, GAM); investigation (LM, GC, WH); supervision (WH, EIP, ISM, GAM); validation (WH);

visualization (GAM); writing – original draft (GAM); writing – review & editing (WH, EIP, ISM, GAM).

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the Engineering & Physical Sciences Research Council [grant numbers EP/P009050/1, EP/P007767/1, EP/M01486X/1, EP/V047078/1, EP/W03395X/1, EP/Y034961/1]. The research leading to these results has received funding from the European Research Council under the European Union's Seventh Framework Programme (FP/2007-2013)/ERC grant agreement no. 320725. Support from the UK Catalysis Hub funded by grant reference EP/R027129/1 is gratefully acknowledged. ISM acknowledges funding from the Royal Academy of Engineering through a Chair in Emerging Technologies Award entitled “Engineering Chemical Reactor Technologies for a Low-Carbon Energy Future” (Grant CiET1819/2/57). GAM was supported by the Royal Academy of Engineering under the Research Fellowship scheme.

Notes and references

- G. A. Mutch, L. Qu, G. Triantafyllou, W. Xing, M. L. Fontaine and I. S. Metcalfe, *J. Mater. Chem. A*, 2019, **7**, 12951–12973.
- W. R. Carper, P. G. Wahlbeck and T. R. Griffiths, *J. Phys. Chem. B*, 2012, **116**, 5559–5567.
- W. Xing, Z. Li, T. Peters, M. L. Fontaine, M. McCann, A. Evans, T. Norby and R. Bredesen, *Sep. Purif. Technol.*, 2019, **212**, 723–727.
- M. Cassir, G. Moutiers and J. Devynck, *J. Electrochem. Soc.*, 1993, **140**, 3114.
- W. Xing, T. Peters, M. L. Fontaine, A. Evans, P. P. Henriksen, T. Norby and R. Bredesen, *J. Membr. Sci.*, 2015, **482**, 115–119.
- M. R. Cerón, L. S. Lai, A. Amiri, M. Monte, S. Katta, J. C. Kelly, M. A. Worsley, M. D. Merrill, S. Kim and P. G. Campbell, *J. Membr. Sci.*, 2018, **567**, 191–198.
- H. Näfe, *ECS J. Solid State Sci. Technol.*, 2014, **3**, N23–N29.
- P. Claes, D. Moyaux and D. Peeters, *Eur. J. Inorg. Chem.*, 1999, **3**, 583–588.
- J. L. Wade, C. Lee, A. C. West and K. S. Lackner, *J. Membr. Sci.*, 2011, **369**, 20–29.
- M. Kazakli, G. A. Mutch, L. Qu, G. Triantafyllou and I. S. Metcalfe, *J. Membr. Sci.*, 2020, **600**, 117855.
- M. Kazakli, G. A. Mutch, G. Triantafyllou, A. G. Gil, T. Li, B. Wang, J. J. Bailey, D. J. L. Brett, P. R. Shearing, K. Li and I. Metcalfe, *J. Membr. Sci.*, 2021, **617**, 118640.
- L. McNeil, G. A. Mutch, F. Iacoviello, J. Bailey, G. Triantafyllou, D. Neagu, T. Miller, E. I. Papaioannou, W. Hu, D. Brett, P. Shearing and I. S. Metcalfe, *Energy Environ. Sci.*, 2020, **13**, 1766–1775.
- I. S. Metcalfe, G. A. Mutch, E. I. Papaioannou, S. Tsochatiridou, D. Neagu, D. J. L. Brett, F. Iacoviello, T. S. Miller, P. R. Shearing and P. A. Hunt, *Nat. Energy*, 2024, **9**, 1074–1083.



- 14 C. G. Mendoza-Serrato, R. López-Juárez, A. Reyes-Montero, J. A. Romero-Serrano, C. Gómez-Yáñez, J. A. Fabián-Anguiano and J. Ortiz-Landeros, *Chem. Eng. Sci.*, 2022, **255**, 117673.
- 15 J. A. Fabián-Anguiano, M. J. Ramírez-Moreno, H. Balmori-Ramírez, J. A. Romero-Serrano, I. C. Romero-Ibarra, X. Ma and J. Ortiz-Landeros, *J. Membr. Sci.*, 2021, **637**, 119607.
- 16 T. T. Norton and Y. S. Lin, *Solid State Ionics*, 2014, **263**, 172–179.
- 17 T. T. Norton, B. Lu and Y. S. Lin, *J. Membr. Sci.*, 2014, **467**, 244–252.
- 18 J. Tong, L. Zhang, M. Han and K. Huang, *J. Membr. Sci.*, 2015, **477**, 1–6.
- 19 L. Zhang, Y. Gong, K. S. Brinkman, T. Wei, S. Wang and K. Huang, *J. Membr. Sci.*, 2014, **455**, 162–167.
- 20 P. Zhang, J. Tong and K. Huang, *J. Mater. Chem. A*, 2017, **5**, 12769–12773.
- 21 J. Fang, J. Tong and K. Huang, *J. Membr. Sci.*, 2016, **505**, 225–230.
- 22 J. Tong, F. Si, L. Zhang and J. Fang, *Chem. Commun.*, 2015, **51**, 2936–2938.
- 23 P. Zhang, J. Tong, Y. Jee and K. Huang, *Chem. Commun.*, 2016, **52**, 9817–9820.
- 24 P. Zhang, J. Tong and K. Huang, *ACS Sustainable Chem. Eng.*, 2018, **6**, 14162–14169.
- 25 J. A. Fabian-Anguiano, R. Ortega-Lugo, M. J. Ramirez-Moreno, B. Zeifert, C. Gomez-Yanez and J. Ortiz-Landeros, *Int. J. Appl. Ceram. Technol.*, 2021, **18**, 1307–1320.
- 26 Z. Xu, Q. Zheng, S. Wang, Z. Zhang, Z. Liu, G. Zhang and W. Jin, *J. Membr. Sci.*, 2021, **635**, 119506.
- 27 S. Wang, J. Tong, L. Cui, P. Zhang and F. Zhou, *J. Membr. Sci.*, 2022, **647**, 120278.
- 28 L. Zhang, J. Tong, Y. Gong, M. Han, S. Wang and K. Huang, *J. Membr. Sci.*, 2014, **468**, 373–379.
- 29 L. Zhang, Y. Gong, J. Yaggie, S. Wang, K. Romito and K. Huang, *J. Membr. Sci.*, 2014, **453**, 36–41.
- 30 Z. Tong, X. Qiao, L. Hou, J. Tong and P. Zhang, *ACS Sustainable Chem. Eng.*, 2024, **12**, 8139–8147.
- 31 A. Gili, B. Bischoff, U. Simon, F. Schmidt, D. Kober, O. Görke, M. F. Bekheet and A. Gurlo, *Membranes*, 2019, **9**, 108.
- 32 G. Zhang, E. I. Papaioannou and I. S. Metcalfe, *Energy Environ. Sci.*, 2015, **8**, 1220.
- 33 L. Grima, G. A. Mutch, P. B. Oliete, W. Bucheli, R. I. Merino, E. I. Papaioannou, J. J. Bailey, M. D. Kok, D. J. L. Brett, P. R. Shearing, I. S. Metcalfe and M. L. Sanjuán, *J. Membr. Sci.*, 2021, **630**, 119057.
- 34 M. Starykevich, A. Jamale, K. A. Yasakau and F. M. B. Marques, *J. Membr. Sci.*, 2022, **659**, 120806.
- 35 A. Jamale, M. Starykevich and F. M. B. Marques, *J. Membr. Sci.*, 2022, **662**, 120968.
- 36 S. Tsocharidou, G. A. Mutch, D. Neagu, E. I. Papaioannou, M. L. Sanjuán, B. Ray, R. I. Merino, V. M. Orera and I. S. Metcalfe, *ACS Appl. Mater. Interfaces*, 2020, **12**, 16436–16441.
- 37 L. Yang, S. Ricote, S. T. B. Lundin and J. D. Way, *Ind. Eng. Chem. Res.*, 2020, **59**, 13706–13715.
- 38 B. Lu and Y. S. Lin, *Ind. Eng. Chem. Res.*, 2014, **53**, 13459–13466.
- 39 B. Lu and Y. S. Lin, *J. Membr. Sci.*, 2013, **444**, 402–411.
- 40 Y. Li, Z. Rui, C. Xia, M. Anderson and Y. S. Lin, *Catal. Today*, 2009, **148**, 303–309.
- 41 O. Ovalle-Encinia and J. Y. S. Lin, *J. Membr. Sci.*, 2022, **646**, 120249.
- 42 O. Ovalle-Encinia and J. Y. S. Lin, *Chem. Eng. J.*, 2022, **448**, 137652.

