

# PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

# On the Faradaic selectivity and the role of surface inhomogeneity during the chlorine evolution reaction at ternary Ti-Ru-Ir mixed metal oxide electrocatalysts

Aleksandar R. Zeradjanin<sup>1,€</sup>, Nadine Menzel<sup>2,&</sup>, Wolfgang Schuhmann<sup>1,\*</sup>, Peter Strasser<sup>2,\*</sup>

<sup>1</sup>Analytical Chemistry and Center for Electrochemical Sciences - CES, Ruhr-Universität Bochum, Universitätsstr. 150, D-44780 Bochum, Germany

<sup>2</sup>The Electrochemical Energy, Catalysis and Material Science Laboratory – Technical University Berlin, Straße des 17. Juni 124, D-10623 Berlin, Germany

**ABSTRACT:** The faradaic selectivity of the chlorine evolution reaction (CER) and oxygen evolution reaction (OER) on the industrially important Ti-Ru-Ir mixed metal oxide is discussed. Absolute evolution rates as well as volume fractions of Cl<sub>2</sub> and O<sub>2</sub> were quantified using differential electrochemical mass spectrometry (DEMS), while the catalyst surface redox behavior was analyzed using cyclic voltammetry. The spatial inhomogeneity of the surface catalytic reaction rate was probed using Scanning Electrochemical Microscopy (SECM). Although the nature of the competition between electrochemical discharging of chloride ions and water molecules remains elusive on a molecular scale, new insight into the spatial reactivity distribution of the CER and OER were obtained. Oxidation of water is the initial step in corrosion and concomitant deactivation of the oxide electrodes, however, at the same time the nature of interaction between the oxide surface and water is used as rational indicator of selectivity and catalytic activity. An experimental procedure was established that will allow studying selectivity of a variety of different catalyst materials using polycrystalline electrode surfaces.

Keywords: selectivity, chlorine, oxygen, DEMS, CV, local chemistry, SECM, ternary oxide, electrocatalysis

---

<sup>€</sup> present address: Max Planck Institute for Iron Research; Interface Chemistry and Surface Engineering, Max Planck Straße 1, D-40237 Düsseldorf, Germany

<sup>&</sup> present address: Fraunhofer Institute for Mechanics of Materials IWM, Walter-Huelse-Straße 1, D-06120 Halle, Germany

## 1. Introduction

Controlling selectivity, while reducing the energy consumption of economically important reaction processes for the purpose of chemical energy conversion or industrial synthesis of chemicals is of high importance, particularly in electrochemical technologies such as brine electrolysis where the chemical reaction is driven by electricity<sup>[1]</sup>. Even though brine electrolysis is an age-old large-scale industrial process, fundamental knowledge of the electrocatalytic reaction, e.g. the impact of the electrode material on the rate of the electrode reaction, which is of outmost importance for improving the reaction efficiency, is still incomplete.<sup>[2-7]</sup> Besides paramount efforts invested in fundamental understanding of electrocatalysis, still many aspects concerning the nature and reactions occurring at the electrochemical interface are not known. The probably main reason for this is the lack of analytical tools and procedures that allow realistic insight into the performance of a given catalyst.<sup>[8]</sup> Identification of critical points in performance of a catalyst is considered to be the basis for rational design of improved or new catalytic materials.<sup>[9]</sup>

This is of particular importance for the understanding of electrocatalytic gas evolving reactions (GER) like the hydrogen evolution reaction (HER), the chlorine evolution reaction (CER) or the oxygen evolution reaction (OER). Especially delicate is the case when OER is a side reaction which needs to be minimized or even completely eliminated. This is the case in CER in which selectivity is a major concern due to the fact that activation of water is a source of an additional oxidation of the transition metal oxides used as catalyst and the main pathway of degradation of the catalyst layer<sup>[10,11]</sup>.

Dimensionally stable anodes (DSA)<sup>[12]</sup> based on ternary oxides<sup>[13–16]</sup> such as e.g. Ti-Ru-Ir oxide had been intensively evaluated, and strategies were proposed for improving stability, activity<sup>[17]</sup>, or selectivity of ternary oxides electrodes during CER and/or OER<sup>[18–20]</sup>. However, despite regions enriched with one of the components are existing on real catalysts usually homogenous mixing of the oxides at atomic level was assumed<sup>[21]</sup>. These local variations in composition are evidently leading to changes in local catalytic activity<sup>[22,23]</sup>.

This work combines a wide array of complementary analytical techniques, such as differential electrochemical mass spectrometry (DEMS) for the quantification of volume fractions of evolved chlorine and oxygen, cyclic voltammetry (CV) for the analysis of surface redox alterations, scanning electron microscopy and energy dispersive X ray spectroscopy (SEM/EDX) for monitoring of Ru displacement and scanning electrochemical microscopy (SECM) for monitoring of changes in the local chemistry. The present results provide new insights into the selectivity, faradaic efficiency and surface reactivity on Ti-Ru-Ir ternary oxide surfaces.

## 2. Experimental part

**Cyclic voltammetry** was performed in a three electrode setup at room temperature. The working electrode was a Ti-Ru-Ir-based dimensionally stable anode (DSA; Bayer Materials, Leverkusen, Germany) in the form of a chip with a diameter ‘d’ of 15 mm. The exposed diameter ‘d<sub>s</sub>’ of the sample during analysis was 5 mm. The reference electrode was a Ag/AgCl/3M KCl electrode (0.207 V/NHE) and the counter electrode was a Pt mesh. Pt mesh and Ag wire was provided by Goodfellow (Bad Nauheim, Germany). 3.5 M NaCl (99.5 %, J.T. Baker, Deventer, The Netherlands) was used as electrolyte. HCl

(37-38%, J.T. Baker, Deventer, The Netherlands) was added until a pH value of 3 was reached. For an estimation of the level of oxidation of the oxide surface during CER NaCl concentrations of 1, 2, 3 and 4 M were used while a pH value of 3 was maintained using HCl and the ionic strength was kept constant using NaNO<sub>3</sub> (99 %, Roth, Karlsruhe, Germany). The potential of the working electrode was controlled by a bipotentiostat/galvanostat (Jaisle PG 100, Waiblingen, Germany). Samples were pre-treated by potential cycling.

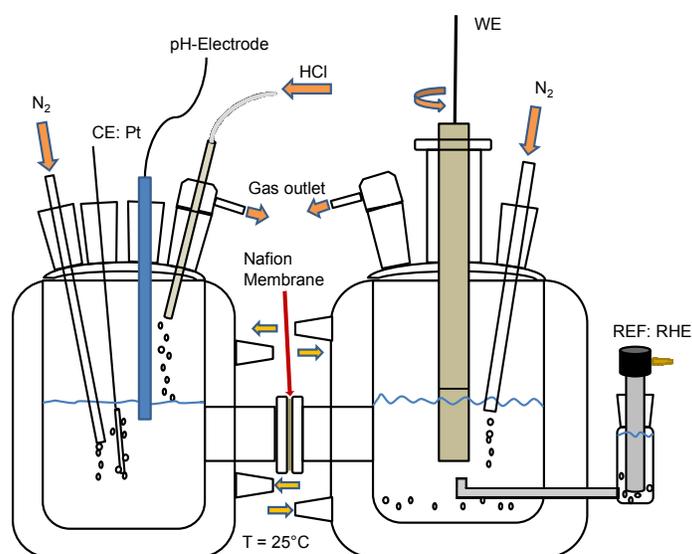


Figure 1: Schematic sketch of the two compartment cell used during the DEMS experiments.

**Differential electrochemical mass spectroscopy.** A mass spectrometer with an integrated gas analytic system (OmniStar GSD 301 C; Pfeiffer Vacuum, Asslar, Germany) and a mass range of 1 to 300 amu was used. A quartz capillary with an inner/outer diameter of 150/220  $\mu\text{m}$ , respectively, was connected to the gas outlet of the electrochemical cell.

Figure 1 shows the two compartment cell used in this study, comprising a separate counter electrode (Pt mesh, Alfa Aesar, Karlsruhe, Germany) chamber with pH value control and a working electrode chamber using a 15 mm diameter Ti-Ru-Ir based DSA

together with a rotating disk electrode setup (PINE Instruments, Raleigh NC, USA) at a rotation rate of 2000 rpm. Galvanostatic measurements were performed at an industrially relevant current density of  $400 \text{ mA/cm}^2$  ( $4 \text{ kA/m}^2$ ) and  $25^\circ\text{C}$  with a flow of  $100 \text{ ml/min}$   $\text{N}_2$  through the working electrode chamber at a pH value of 3 and electrolyte concentrations of 1, 2, 3 and 4 M NaCl (99,5%, ChemPur, Karlsruhe, Germany). The reference electrode was a reversible hydrogen electrode (RHE, Gaskatel, Kassel, Germany) which was separated from the working electrode chamber by means of a Haber-Luggin capillary. All electrochemical measurements were controlled by a Gamry Reference 3000 potentiostat/galvanostat (C3 Prozess- und Analysetechnik, Haar, Germany). Calibration of the mass spectrometer with  $\text{N}_2$  ( $100 \text{ ml/min}$ ),  $\text{O}_2$  ( $50 \text{ ml/min}$ ) and  $\text{Cl}_2$  ( $50 \text{ ml/min}$ ) was performed using mass flow controllers (Bronkhorst Mättig, Kamen, Germany).


**Scanning electron microscopy and energy dispersive X-ray spectroscopy.** SEM/EDX mapping was done using a FEI ESEM Dual Beam Quanta 3D FEG electron microscope equipped with an EDAX Genesis XM2i EDX system. The spatial distribution of Ru was monitored before and after electrolysis.

**Scanning electrochemical microscopy (SECM).** A modified SECM set-up (Sensolytics, Bochum, Germany) was used. The local activity of the electrodes for CER was evaluated using the sample-generator/tip-collector (SG/TC) and the redox competition (RC) modes of SECM. Details of the measurement strategy and its validity have been described previously<sup>[24]</sup>. Samples with an area of  $15 \text{ mm}$  in diameter were used exposing only a diameter ' $d_s$ ' of the sample of  $5 \text{ mm}$  during analysis. The SECM tip current is a measure of the catalytic activity of the sample underneath the tip. In the SG/TC mode the SECM

tip (Pt microelectrode, 25  $\mu\text{m}$ ) was used for scanning of the sample at a tip-to-sample distance of 20  $\mu\text{m}$ . The sample was continuously polarized at a potential of 1.4 V vs. Ag/AgCl for invoking CER by oxidation of  $\text{Cl}^-$  while the Pt-tip was polarized at a potential of 0.950 V vs. Ag/AgCl to detect changes in the local  $\text{Cl}_2$  concentration caused by the reaction at the sample. In the RC-mode was used to investigate local equilibrium perturbations. The sample was polarized at potentials in the interval from 1.3 to 2.0 V vs. Ag/AgCl while the tip potential was 1.4 V vs. Ag/AgCl. The electrolyte was 5 M NaCl (pH 2). SECM measurements were carried out at room temperature. Data processing was done using OriginPro8G (OriginLab, Northampton MA, USA) and Mira (G. Wittstock, University Oldenburg).

### 3. Results and discussion

In a concentrated aqueous solution of NaCl both OER and CER can occur during anodic polarization at potentials above 1.05 V vs. Ag/AgCl/3M KCl (see Reaction (1) Reaction (2)). The OER is thermodynamically favored over CER. This is why the faradaic selectivity of the CER is an important concern and has to be addressed. The two half-cell processes proceed according:



To quantify the faradaic selectivity of each process, that is the electric charge used exclusively for either reaction, differential electrochemical mass spectrometry (DEMS) was utilized<sup>[25]</sup> (

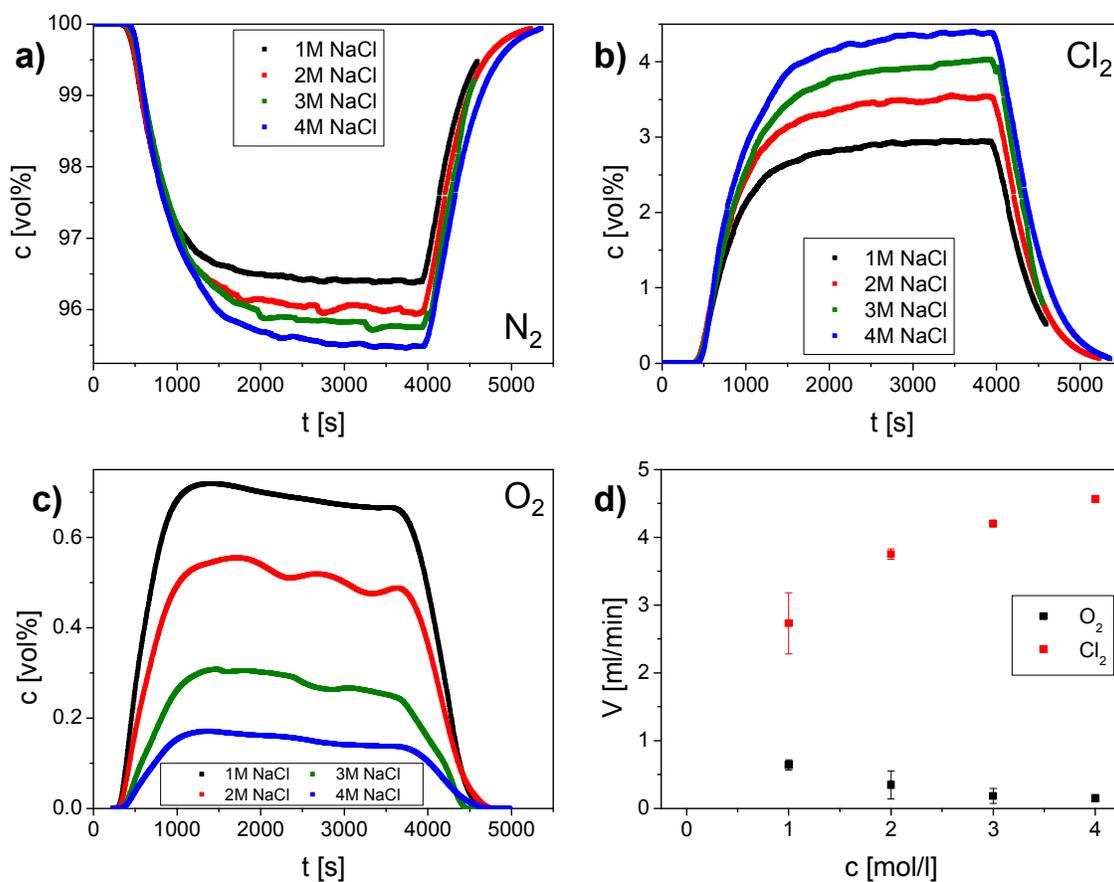


Figure 2). Gas monitoring and galvanostatic polarization were initiated at the same time ( $t = 0$  s). After an initial phase ( $\sim 500$  s) a decrease of the nitrogen carrier stream (

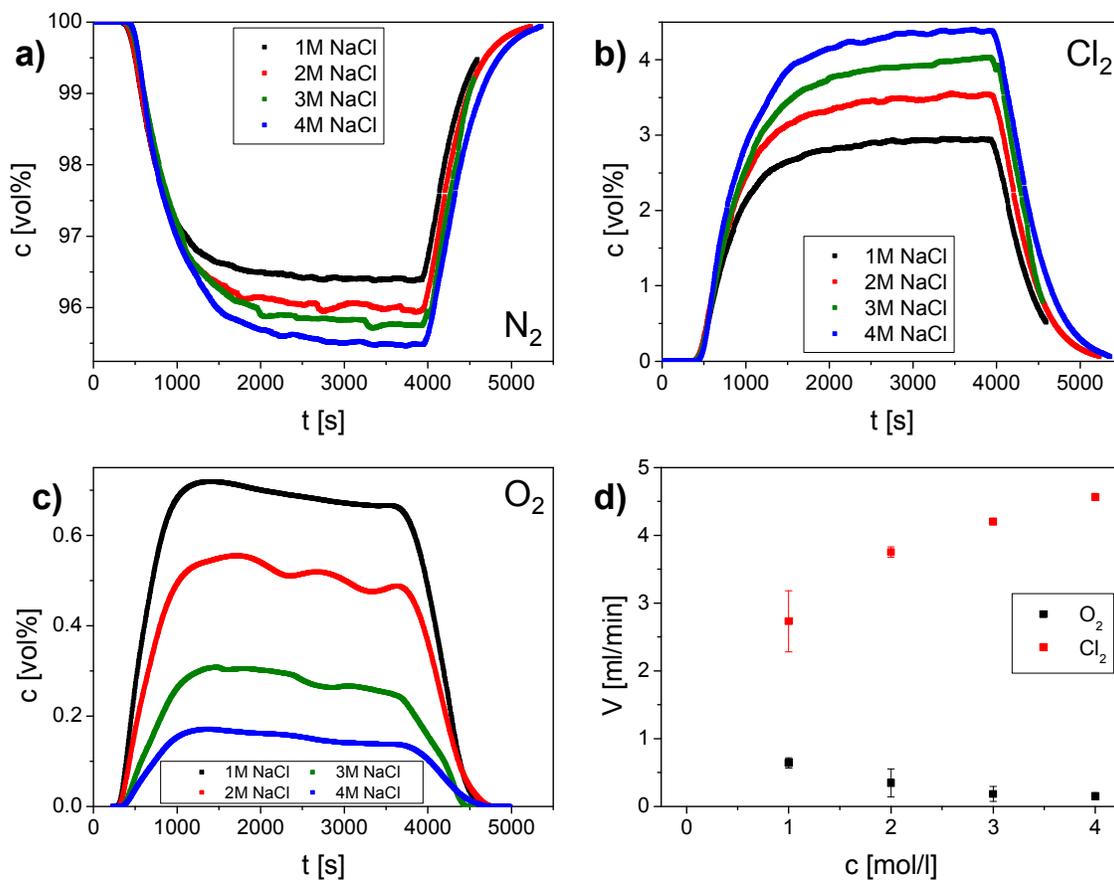


Figure 2a) and an increase of the evolved oxygen and chlorine (

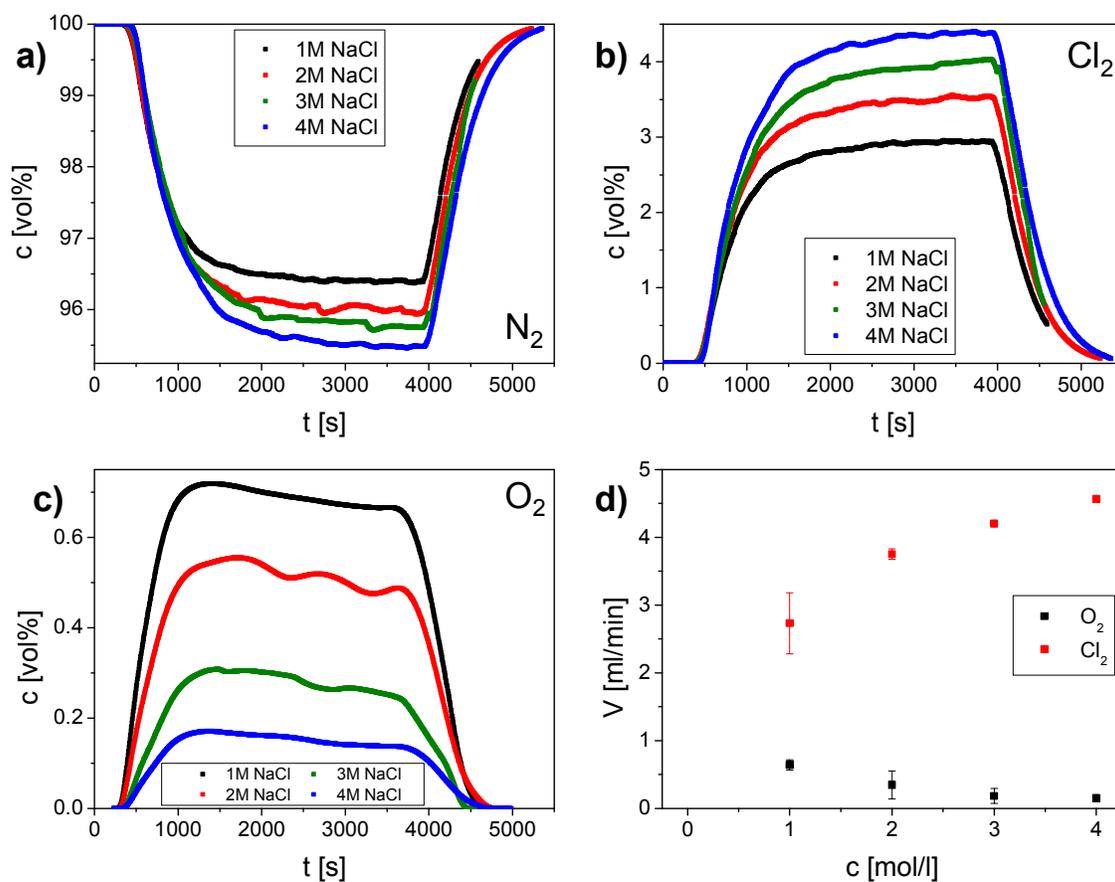


Figure 2b and

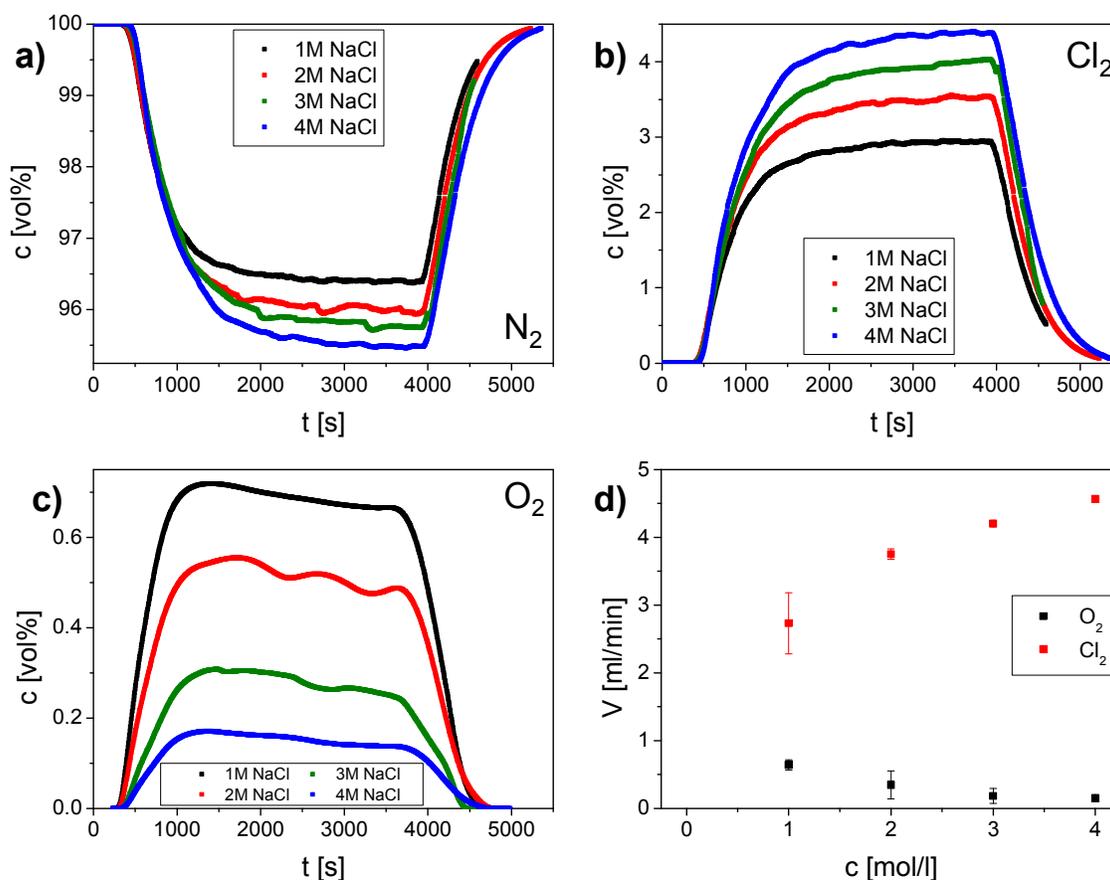


Figure 2c) was observed. The gas evolution was monitored until it reached a stationary state after about 3600 s when the electrochemical cell was switched off. An increase of the nitrogen carrier stream and a decrease of the evolved gas were observed after around 400 s. According to literature, OER is supposed to be negligible already at 0.1 M NaCl<sup>[26]</sup>. However, our data here evidence that molecular oxygen is co-evolved even in an electrolyte containing 4 M NaCl (

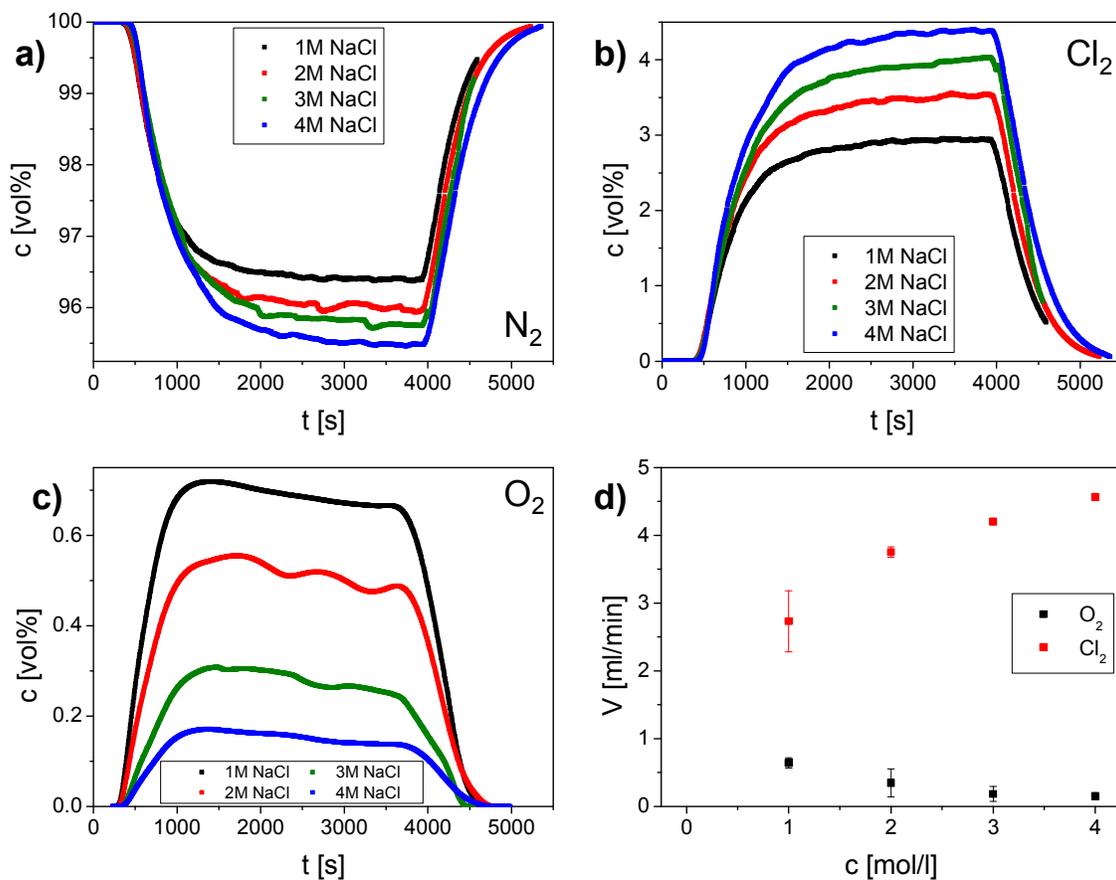


Figure 2).

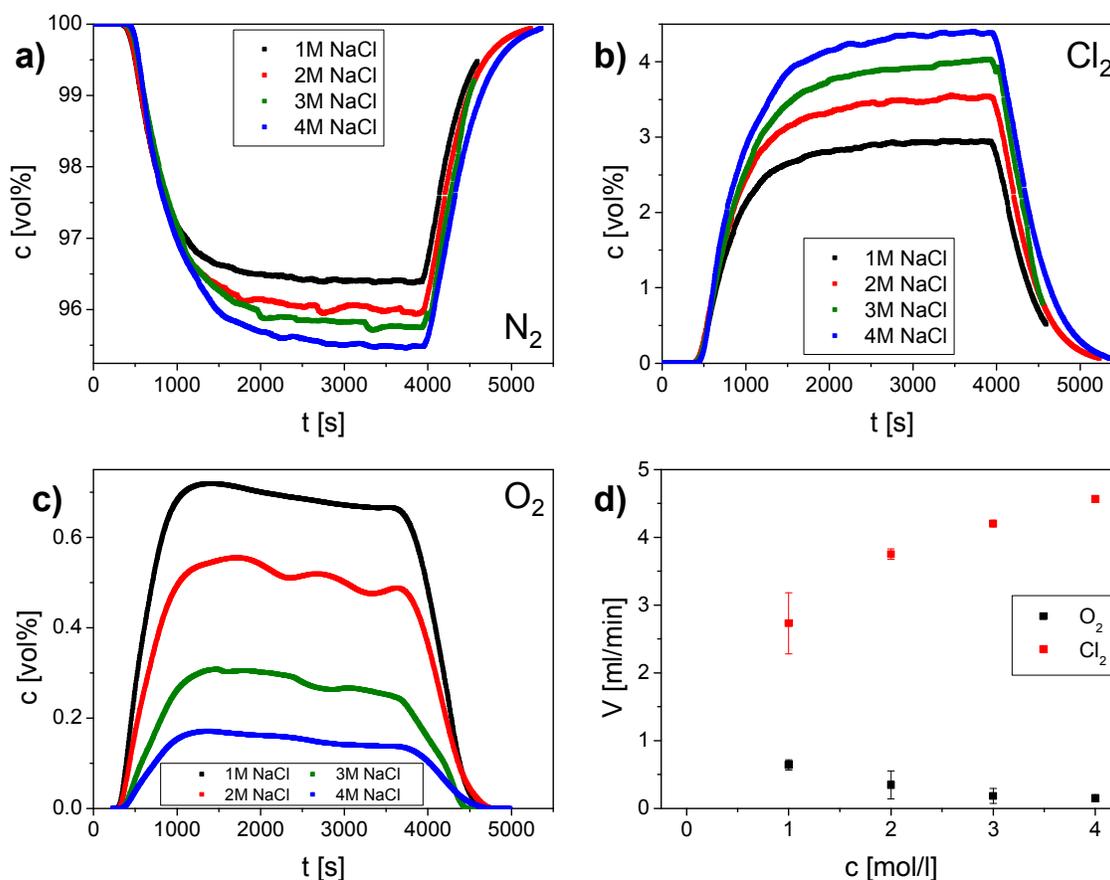


Figure 2. Monitoring the selectivity of the CER at Ti-Ru-Ir based ternary oxide using DEMS for four different concentrations of aqueous NaCl solution. The current density was  $400 \text{ mA/cm}^2$  and the temperature was  $25^\circ\text{C}$ . Example volume fractions of: a)  $\text{N}_2$  (inert gas carrier) b)  $\text{Cl}_2$  (main product) and c)  $\text{O}_2$  (side product); d) calculated flows in ml/min for  $\text{Cl}_2$  and  $\text{O}_2$  as a function of concentration of  $\text{Cl}^-$  ions.

Stationary volumetric flows of  $\text{Cl}_2$  and  $\text{O}_2$  ( $V_x$ , Table 1, Columns 5-6) were calculated using the measured volume fractions ( $c_x$ , To calculate the theoretical flow rates the number of electrons  $z$  was 2 in the case of the chlorine evolution reaction and 4 for the oxygen evolution reaction.

Table 1, Column 2-4) and the large, quasi-constant flow rate of nitrogen ( $V_{\text{N}_2}$ ) according to:

$$\dot{V}_x = \frac{c_x}{c_{N_2}} \cdot \dot{V}_{N_2} \quad \text{Equation (1)}$$

These stationary gas evolution flow rates represent the electrochemical yields of each gas product. From the calculated flow rates of Cl<sub>2</sub> and O<sub>2</sub> the “selectivity S (To calculate the theoretical flow rates the number of electrons z was 2 in the case of the chlorine evolution reaction and 4 for the oxygen evolution reaction.

Table 1, Column 7) for CER was calculated as the ratio between the flow of Cl<sub>2</sub> and the sum of the flows for Cl<sub>2</sub> and O<sub>2</sub>. The gas current efficiency (To calculate the theoretical flow rates the number of electrons z was 2 in the case of the chlorine evolution reaction and 4 for the oxygen evolution reaction.

Table 1, Column 8-9) was derived by taking the ratio of the measured flow rates of Cl<sub>2</sub> and O<sub>2</sub> and their corresponding theoretical flow rates (V<sub>theo</sub>) calculated using the total applied current and assuming ideal gas behavior according to::

$$\dot{V}_{\text{theo}} = \frac{V}{t} = \frac{I \cdot R \cdot T}{z \cdot F \cdot p} \quad \text{Equation (2)}$$

To calculate the theoretical flow rates the number of electrons z was 2 in the case of the chlorine evolution reaction and 4 for the oxygen evolution reaction.

Table 1. Data from DEMS measurements for the estimation of selectivity and faradaic efficiency.

c <sub>chloride</sub> [M]	c [vol%]			V [ml/min]		selectivity S [%]	gas current efficiency [%]	
	N <sub>2</sub>	O <sub>2</sub>	Cl <sub>2</sub>	O <sub>2</sub>	Cl <sub>2</sub>	Cl <sub>2</sub>	Cl <sub>2</sub>	Cl <sub>2</sub> + O <sub>2</sub>
NaCl								

1	96.77	0.63	2.60	0.65 ± 0.04	2.69 ± 0.36	80 ± 1	50 ± 7	74 ± 8
2	96.09	0.33	3.58	0.35 ± 0.14	3.72 ± 0.05	91 ± 3	69 ± 1	82 ± 4
3	95.77	0.20	4.03	0.21 ± 0.10	4.21 ± 0.05	95 ± 2	78 ± 1	85 ± 3
4	95.48	0.15	4.36	0.16 ± 0.01	4.57 ± 0.01	97 ± 1	84 ± 1	90 ± 1

From DEMS measurements it becomes clear that the selectivity  $S$  for CER increases with increasing chloride concentration and reaches nearly 100 % for chloride concentrations above 3 M (Table 1). This can be rationalized by a competition between chloride ions and water molecules for active surface sites considering the experimentally determined kinetic exponent of one for chloride ions during CER. Anodic water activation, which was identified to be the main source of corrosion of DSA, initiates further oxidation of the oxide surface under formation of unstable higher oxidation states of  $\text{RuO}_x$  according to<sup>[27]</sup>.



The values of the gas current efficiency of 74 to 90% (Table 1, column 9) confirm charge consumption due to parasitic processes such as e.g. surface oxidation.

Cyclic voltammetry (CV) was used to estimate the level of oxidation of the surface during the CER (**Figure 3**). CVs of the Ti-Ru-Ir based DSA were recorded with the same scan rate, in the same potential range, at the same pH value, however, at different concentrations of NaCl (**Figure 3a**).

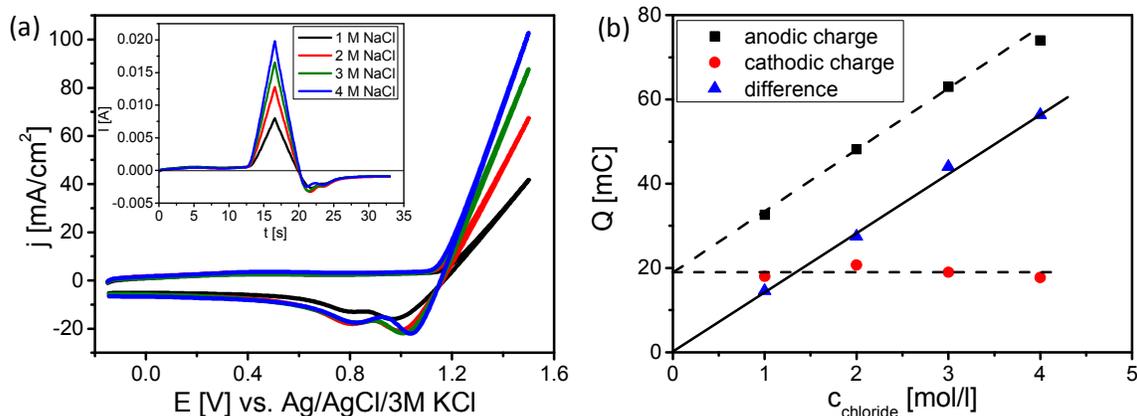


Figure 3. a) Cyclic voltammograms of the Ti-Ru-Ir ternary oxide based DSA in 1, 2, 3 and 4 M aqueous solution of NaCl at a scan rate of 100 mV/s and a pH value of 2. The ionic strength was kept constant using NaNO<sub>3</sub>. The inset shows same cyclic voltammogram transformed into the time domain. b) Charge during the anodic sweep (black cubes), charge during the cathodic sweep (red circles) and the difference charge (blue triangles).

As expected, with increasing Cl<sup>-</sup> concentrations higher currents are observed (Figure 3a).

Converting the recorded CVs into the time domain (inset of **Figure 3a**) demonstrates that the charge consumed during the anodic sweep increases with the Cl<sup>-</sup> concentration while the charge during the cathodic sweep is almost constant. Integration of the current over time plot (inset of **Figure 3a**) demonstrates that the charge consumed during the anodic sweeps increases linearly with the Cl<sup>-</sup> concentration. This can be easily understood as the total amount of the produced gases (Cl<sub>2</sub> + O<sub>2</sub>) is increasing with the availability of Cl<sup>-</sup> ions. It is hence expected that the extrapolation of the dependence between anodic charge and should go nearly through the origin due to the fact that the contribution of OER is supposed to be small (below 20%). However, extrapolation to zero Cl<sup>-</sup> concentration leads to a residual charge of about 20 mC. It was supposed that CER and OER are increasing in parallel during concomitant oxidation of the DSA surface during the anodic sweep and that reduction of Cl<sub>2</sub> and O<sub>2</sub> further proceeds during the cathodic sweep while the previously oxidized surface is reduced. However, the charge transferred during the

cathodic sweep is identical for all four concentrations of NaCl. Either reduction of  $\text{Cl}_2$  and  $\text{O}_2$  is almost negligible at the observed current densities due to a rapid convective transport of  $\text{Cl}_2$  and  $\text{O}_2$  away from the rotating solid/liquid interface towards the gas phase. In this case, the charge transferred during the cathodic sweep arises at least predominantly from the reduction of the higher oxide formed during the anodic sweep. Subtracting the cathodic charge i.e. the charge needed for the reduction of the oxide from the charge during the anodic half scan, the linear correlation of the difference charge and the  $\text{Cl}^-$  concentration starts at zero (see **Figure 3b**). Thus, taking into consideration the current efficiencies as obtained in the stationary measurements (Table 1) and the non-stationary measurements we conclude that the constant amount of charge is used for catalyst oxidation.

In an earlier analysis of CER<sup>[28]</sup> the reaction rate as expressed by the exchange current density was correlated with parameters describing the intrinsic catalytic behavior. Importantly it was found that an increase in the exchange current density corresponds to a decreased charge necessary for the oxidation of the catalyst surface during CER. Thus, the oxidation of the catalyst surface can be interpreted as a redox process that is associated with compositional, geometric and/or electronic alteration processes of the surface or near-surface region promoting the formation of active sites for CER (or OER). The catalytically active sites are non-stoichiometric oxides with coordinately unsaturated sites. Evidently, during anodic polarization,  $\text{RuO}_x$  is converted to a higher oxidation state while simultaneously  $\text{Cl}^-$  ions or water molecules located in the inner Helmholtz plane partially compensate the charge from their free electron pair(s) into the vacant d-orbitals of the transition metal. This is at least partly re-reducing  $\text{RuO}_x$ . The correlation of the

kinetics of CER and OER with the enthalpy of the bulk oxidation of  $\text{RuO}_x$ <sup>[4]</sup> as well as with the binding energy of the adsorbed species<sup>[5]</sup> does not sufficiently explain the observed catalytic activity. It was proposed that for a facilitated electrocatalytic reaction the redox potential for the transition from the lower to the higher oxidation state of  $\text{RuO}_x$  has to be close to the potential of the catalyzed reaction<sup>[29,30]</sup>. Evidently, if the reaction occurred at low potentials the catalytic process could not contribute to prevent overoxidation of the surface causing a decrease of the catalytic activity. However, even though the voltammetric surface redox properties can be correlated with the intrinsic catalytic properties of a catalyst, the low Faradaic efficiency of only 88% has to be due to a parasitic chemical reaction which consumes electricity. This aspect is generally not discussed and is not accessible using conventional electroanalytical methods.

In order to gain deeper understanding of the catalytic performance of ternary oxides for CER and OER we focused on the correlation of experimental selectivity and spatial distribution of surface catalytic activity. To achieve this, we analyzed the local catalytic properties of the ternary catalyst coatings. The selectivity of CER is decreasing if the relative amount of  $\text{RuO}_2$  in the ternary oxide becomes too high. In the case of a  $\text{Ti}/(\text{TiO}_2+\text{RuO}_2)$  DSA with 40 mol%  $\text{RuO}_2$  OER becomes more significant<sup>[31]</sup>. Thus, the potential local enrichment of  $\text{RuO}_2$  was evaluated. The morphology of the investigated DSA coating are shown in **Figure 4a** together with an EDX elemental map over the same region (**Figure 4b**). Surface enrichment of Ru can be seen.

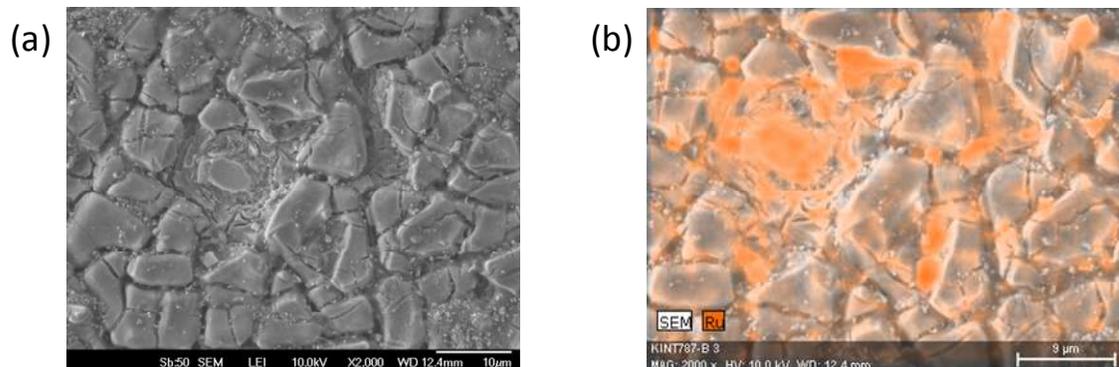


Figure 4. a) SEM micrograph of the morphological surface structure of a ternary Ti-Ru-Ir oxide DSA. b) EDX confirms local Ru enrichment at the electrode surface after electrochemical testing.

Due to the local accumulation of  $\text{RuO}_x$  the selectivity between CER and OER is modulated at these sites in favor of OER.

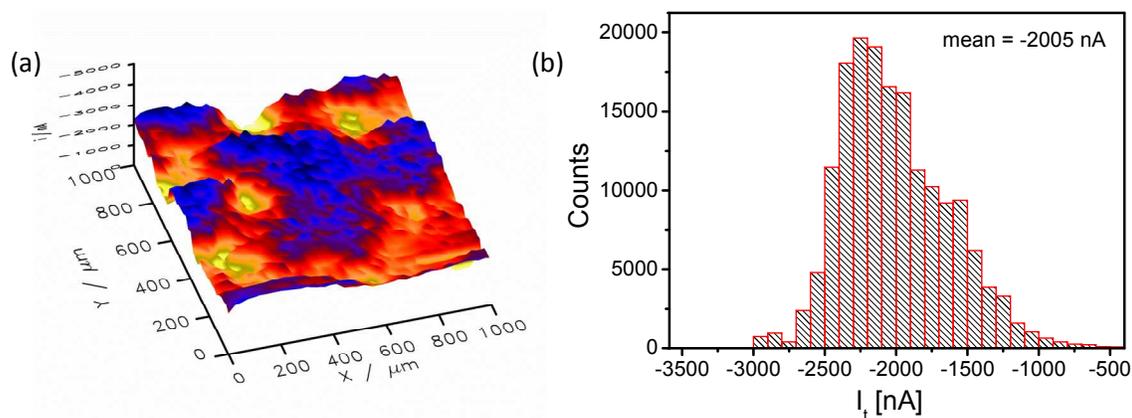


Figure 5. a) 3D SECM image of  $1000 \times 1000 \mu\text{m}^2$  region of the ternary oxide based DSA obtained in the sample-generator/tip-collector mode representing the spatial electrocatalytic activity. (Tip potential  $E_t = 950 \text{ mV}$ ; sample potential  $E_s = 1400 \text{ mV}$  vs.  $\text{Ag}/\text{AgCl}/3 \text{ M KCl}$ ). b) Current distribution histogram extracted from the tip currents of the SECM image in a).

**Figure 5** shows a SECM image of a selected area of the catalyst layer.  $\text{Cl}_2$  generated at the sample is reduced at the microelectrode tip (Pt disk,  $25 \mu\text{m}$  diameter), thus, visualizing the local CER activity via the tip current. The SECM image is – even at the resolution determined by the rather large tip diameter – displaying local modulations of the electrocatalytic activity (**Figure 5a**) in accordance with the EDX mapping (compare

Figure 4b). Obviously, the nanostructured catalyst surface that exhibited a rather homogenous composition after synthesis is locally modified due to surface compositional and structural changes.

The current distribution histogram (**Figure 5b**) illustrates the large local variation in the catalytic activity of the sample and hence the amount of generated  $\text{Cl}_2$ . The lowest and highest current values differ by a factor of almost 6 (from -500 to -3000 nA). In the spatial distribution of the electrocatalytic activity (**Figure 5a**) two characteristic areas can be distinguished, namely one area with very low activity ( $x = 450 \mu\text{m}$ ,  $y = 950 \mu\text{m}$ ) and one with very high activity ( $x = 500 \mu\text{m}$ ,  $y = 700 \mu\text{m}$ ).

The SECM tip was positioned above these areas and a redox-competition mode experiment was performed in which the SECM tip is polarized to 1400 mV vs. Ag/AgCl to compete with the sample for the available  $\text{Cl}^-$  ions in the gap between tip and sample (**Figure 6**). In the redox competition mode a more active site is recognized by a sharper decrease of the anodic tip current. The tip senses the concentration ratio  $[\text{Cl}_2]/[\text{Cl}^-]$  near the sample surface which differs from the one in the bulk of the electrolyte. Upon increasing of the sample potential the tip current initially decreases as expected. However, the tip current even changed to cathodic despite the applied tip potential of 1400 mV. Evidently, due to the high concentration of the formed  $\text{Cl}_2$  at the sample and the completely diminished  $\text{Cl}^-$  concentration in the gap between tip and sample the Nernst potential of the  $\text{Cl}_2/2\text{Cl}^-$  redox couple is sufficiently high that  $\text{Cl}_2$  reduction at the tip becomes possible (**Figure 6b**). The sample potential at which the tip current changes from anodic to cathodic is the equilibrium point at which the local Nernst potential of the  $\text{Cl}_2/2\text{Cl}^-$  redox couple is equal to the applied tip potential. For a less active sample area

the initial anodic tip current is higher and the applied sample potential has to be higher for the transition from anodic to cathodic tip current.

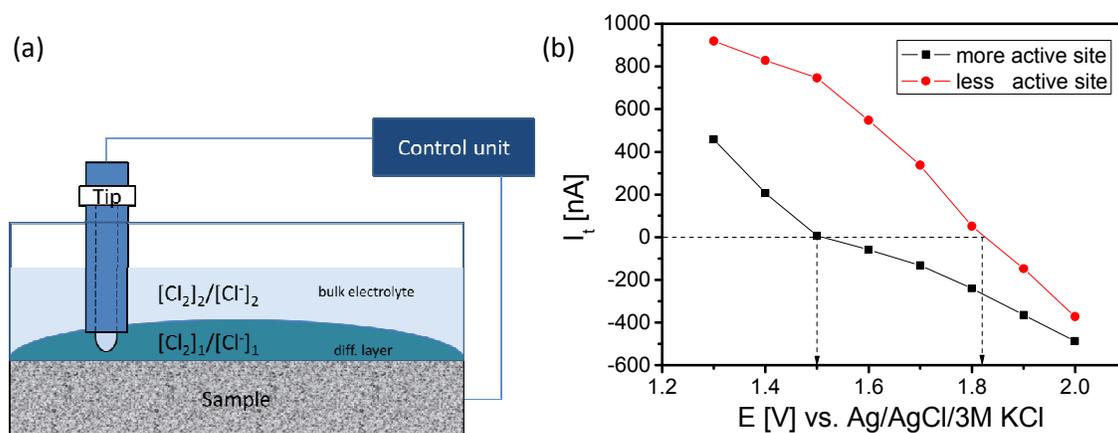


Figure 6. a) Scheme of a section of the DSA sample during SECM imaging. The SECM tip senses the  $[\text{Cl}_2]/[\text{Cl}^-]$  concentration ratio near the electrode surface which differs from the one in the bulk of the electrolyte. b) Tip current ( $E_{\text{tip}} = 1400 \text{ mV/Ag/AgCl/3M KCl}$ ) in proximity of the sample as a function of the applied sample potential over two sample regions with different catalytic activity. The point of transformation of anodic to cathodic tip current refers to the equilibrium between the potential at the tip and potential of the  $\text{Cl}_2/2 \text{ Cl}^-$  redox couple.

While the ohmic drop at the tip is supposed to be negligible due to the small current response, the local value of the potential at the sample depends on the ohmic drop. The ohmic resistance was estimated using electrochemical impedance spectroscopy keeping the distance between sample and reference electrode constant at 1 cm. The obtained value of  $15 \Omega$ , is supposed to be representative for both sample areas because their distance is negligible in comparison to the distance from the reference electrode assuming that the main contribution to the ohmic resistance is from the electrolyte with its gas fraction. At potentials of e.g. 1.5 V and 1.8 V vs. Ag/AgCl, the potentials at which the tip currents change from anodic to cathodic for the two different sample areas, the measured sample currents and derived ohmic drops were 6.1 mA and 92 mV as well as 12.8 mA and 192 mV, respectively. Thus, the local electrode potential at the highly active site was around 1.41 V vs. Ag/AgCl while the local electrode potential at the site with low activity was

around 1.63 V vs. Ag/AgCl. Surprisingly, the potential difference between two adjacent sites of a DSA can be as high as 200 mV. Taking into account the local Nernst potential of the  $\text{Cl}_2/2\text{Cl}^-$  redox couple it becomes possible that during  $\text{Cl}_2$  formation at one site of the sample  $\text{Cl}_2$  can be simultaneously reduced at an adjacent site with lower catalytic activity. Consequently, the efficiency and selectivity of CER and OER strongly depend on the control of the local properties of the catalytic surface and in particular on the spatial distribution of the catalytically active sites.

#### 4. Conclusions

The evaluation of the selectivity of simultaneously occurring OER and CER at a ternary Ti-Ru-Ir oxide based DSA sample was performed by combining DEMS and CV. The selectivity of CER over OER is high and is increasing with the  $\text{Cl}^-$  ion concentration to 97% as confirmed by DEMS. The gas current efficiency was constant with values of 80-90% for all  $\text{Cl}^-$  concentrations. The remaining faradaic current is used for the oxidation of the catalyst surface. CV measurements additionally revealed that the inevitable oxidation of the catalyst surface is not only a consequence of the simultaneously occurring OER, but rather an important part of the process of formation of active surface sites which is unequivocally necessary for sustained efficient CER. However, the faradaic efficiency was only 88% which suggested evaluating local properties of the catalyst surface. On the one hand, the displacement of Ru causing a high density of active sites at some regions may be responsible for an inhomogeneous distribution of the current density. Using SECM in the redox competition mode allowed extracting sample potentials for

differently active sample areas at which the tip current changed from anodic to cathodic. This suggests that due to local varying equilibria between the sample potential and the local Nernst potential of the  $\text{Cl}_2/2 \text{Cl}^-$  redox couple the anodically produced  $\text{Cl}_2$  can be re-reduced at nearby sites of the same DSA surface. This could explain the “disappearance” of charge used for electrolysis.

## 5. ACKNOWLEDGMENTS

The authors are grateful to the BMBF in the framework of the project „Innovative Technologien für Ressourceneffizienz rohstoffintensiver Produktionsprozesse: Effizienzsteigerung bei der Chlorherstellung“ (FKZ: 033R018E). Financial support by the German Research Foundation (DFG) through grant STR 596/3-1 under the Priority Program 1613 “Regeneratively formed fuels by light driven water splitting” is gratefully acknowledged.

## 6. REFERENCES

- [1] S. Trasatti, *Electrochim. Acta* **2000**, *45*, 2377–2385.
- [2] J. O. Bockris, *Science* **1972**, *176*, 1323–1323.
- [3] B. E. Conway, B. V. Tilak, *Electrochim. Acta* **2002**, *47*, 3571–3594.
- [4] S. Trasatti, *Electrochim. Acta* **1984**, *29*, 1503–1512.
- [5] I. C. Man, H.-Y. Su, F. Calle-Vallejo, H. A. Hansen, J. I. Martínez, N. G. Inoglu, J. Kitchin, T. F. Jaramillo, J. K. Nørskov, J. Rossmeisl, *ChemCatChem* **2011**, *3*, 1159–1165.
- [6] H. Dau, C. Limberg, T. Reier, M. Risch, S. Roggan, P. Strasser, *ChemCatChem* **2010**, *2*, 724–761.

- [7] I. Katsounaros, S. Cherevko, A. R. Zeradjanin, K. J. J. Mayrhofer, *Angew. Chem. Int. Ed.* **2014**, *53*, 102–121.
- [8] A. R. Zeradjanin, E. Ventosa, A. S. Bondarenko, W. Schuhmann, *ChemSusChem* **2012**, *5*, 1905–1911.
- [9] A. S. Bandarenka, E. Ventosa, A. Maljusch, J. Masa, W. Schuhmann, *The Analyst* **2014**, *139*, 1274.
- [10] A. R. Zeradjanin, A. A. Topalov, Q. Van Overmeere, S. Cherevko, X. Chen, E. Ventosa, W. Schuhmann, K. J. J. Mayrhofer, *Rsc Adv.* **2014**, *4*, 9579.
- [11] G. N. Martelli, R. Ornelas, G. Faita, *Electrochim. Acta* **1994**, *39*, 1551–1558.
- [12] H. B. Beer, *J. Electrochem. Soc.* **1980**, *127*, 303C.
- [13] T. A. F. Lassali, J. F. C. Boodts, S. Trasatti, *Electrochim. Acta* **1994**, *39*, 1545–1549.
- [14] L. A. De Faria, J. F. C. Boodts, S. Trasatti, *Electrochim. Acta* **1997**, *42*, 3525–3530.
- [15] N. Menzel, E. Ortel, K. Mette, R. Kraehnert, P. Strasser, *ACS Catal.* **2013**, *3*, 1324–1333.
- [16] K. C. Neyerlin, G. Bugosh, R. Forgie, Z. Liu, P. Strasser, *J. Electrochem. Soc.* **2009**, *156*, B363.
- [17] J. F. C. Boodts, *J. Electrochem. Soc.* **1990**, *137*, 3784.
- [18] K. Macounová, M. Makarova, J. Jirkovský, J. Franc, P. Krtil, *Electrochim. Acta* **2008**, *53*, 6126–6134.
- [19] V. Petrykin, K. Macounova, O. A. Shlyakhtin, P. Krtil, *Angew. Chem.* **2010**, *122*, 4923–4925.
- [20] V. Petrykin, K. Macounova, J. Franc, O. Shlyakhtin, M. Klementova, S. Mukerjee, P. Krtil, *Chem. Mater.* **2011**, *23*, 200–207.
- [21] J. Gaudet, A. C. Tavares, S. Trasatti, D. Guay, *Chem. Mater.* **2005**, *17*, 1570–1579.
- [22] R. Chen, V. Trieu, A. R. Zeradjanin, H. Natter, D. Teschner, J. Kintrup, A. Bulan, W. Schuhmann, R. Hempelmann, *Phys. Chem. Chem. Phys.* **2012**, *14*, 7392.
- [23] A. R. Zeradjanin, F. La Mantia, J. Masa, W. Schuhmann, *Electrochim. Acta* **2012**, *82*, 408–414.
- [24] A. R. Zeradjanin, T. Schilling, S. Seisel, M. Bron, W. Schuhmann, *Anal. Chem.* **2011**, *83*, 7645–7650.
- [25] M. Wohlfahrt-Mehrens, J. Heitbaum, *J. Electroanal. Chem. Interfacial Electrochem.* **1987**, *237*, 251–260.
- [26] S. Ardizzone, *J. Electrochem. Soc.* **1982**, *129*, 1689.
- [27] A. R. Zeradjanin, N. Menzel, P. Strasser, W. Schuhmann, *ChemSusChem* **2012**, *5*, 1897–1904.
- [28] P. Gu, Doctoral Thesis, University of Ottawa, Canada, **1990**.
- [29] Y. Matsumoto, E. Sato, *Mater. Chem. Phys.* **1986**, *14*, 397–426.
- [30] A. C. C. Tseung, S. Jasem, *Electrochimica Acta* **1977**, *22*, 31–34.
- [31] L. D. Burke, O. J. Murphy, *J. Electroanal. Chem. Interfacial Electrochem.* **1980**, *109*, 199–212.