

Cite this: *Chem. Sci.*, 2023, 14, 3415

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Addressing the stability challenge of photo(electro) catalysts towards solar water splitting

Mu Xiao, <sup>a</sup> Zhiliang Wang, <sup>a</sup> Kazuhiko Maeda, <sup>b</sup> Gang Liu <sup>cd</sup> and Lianzhou Wang <sup>\*a</sup>

The efficiency and stability of photo(electro)catalytic devices are the main criteria towards practical solar fuel production. The efficiency of photocatalysts/photoelectrodes has been intensively pursued and significant progress has been achieved over the past decades. However, the development of durable photocatalysts/photoelectrodes remains one of the biggest challenges for solar fuel production. Moreover, the lack of a feasible and reliable appraisal procedure makes it difficult to evaluate the durability of photocatalysts/photoelectrodes. Herein, a systematic process is proposed for the stability evaluation of photocatalysts/photoelectrodes. A standard operational condition should be used for the stability assessment and the stability results should be reported with the run time, operational stability, and material stability. A widely adopted standardisation for stability assessment will benefit the reliable comparison of results from different laboratories. Furthermore, the deactivation of photo(electro) catalysts is defined as a 50% decrease in productivity. The purpose of the stability assessment should aim to figure out the deactivation mechanisms of photo(electro)catalysts. A deep understanding of the deactivation mechanisms is essential for the design and development of efficient and stable photocatalysts/photoelectrodes. This work will provide insights into the stability assessment of photo(electro)catalysts and advance practical solar fuel production.

Received 21st December 2022  
Accepted 23rd February 2023

DOI: 10.1039/d2sc06981d

rsc.li/chemical-science

<sup>a</sup>School of Chemical Engineering, Australian Institute for Bioengineering and Nanotechnology, The University of Queensland, QLD, 4072, Australia. E-mail: l.wang@uq.edu.au

<sup>b</sup>Department of Chemistry, School of Science, Tokyo Institute of Technology, Tokyo 152-8551, Japan

<sup>c</sup>Shenyang National Laboratory for Materials Science, Institute of Metal Research, Chinese Academy of Sciences, Shenyang 110016, China

<sup>d</sup>School of Materials Science and Engineering, University of Science and Technology of China, Shenyang 110016, China

## 1. Introduction

Solar fuel production *via* photo(electro)catalytic technology presents a sustainable solution to address energy and environmental challenges facing the global community.<sup>1–3</sup> Up to date, the efficiency and device durability of photo(electro)catalytic devices remain major challenges towards low-cost solar fuel production.<sup>4,5</sup> The cost of H<sub>2</sub> is US\$1.03–2.16 kg<sup>−1</sup> produced from commercial steam methane reforming.<sup>6</sup> An energy



Mu Xiao is a postdoctoral research fellow at the School of Chemical Engineering, The University of Queensland (UQ). She received her Bachelor's degree in materials science and engineering from Huazhong University of Science and Technology in 2012 and PhD degree in materials engineering from UQ in 2019. Dr Xiao's research focuses on the development and design of semiconducting nano-

materials for solar energy conversion.



Zhiliang Wang is an Australian Research Council (ARC) Discovery Early Career Fellow at the School of Chemical Engineering, The University of Queensland. He received his Bachelor's degree from Central South University in 2011 and PhD degree from the Dalian Institute of Chemical Physics, University of Chinese Academy of Sciences in 2017. Dr Wang's research focus is on the design,

synthesis and characterisation of semiconductor materials for the application of solar conversion.

efficiency of 10% and a lifetime of up to 5 years are required accordingly to enable cost-competitive  $\text{H}_2$  production *via* solar-driven photocatalytic water splitting.<sup>7</sup> The overall efficiency of the photo(electro)catalytic solar energy conversion has been remarkably enhanced over the past decade but suffers from poor stability.<sup>8,9</sup> For instance, a photocurrent of  $12.1 \text{ mA cm}^{-2}$  (at 1.23 V vs. reversible hydrogen electrode, RHE) has been achieved on an integrated  $\text{Ta}_3\text{N}_5$  photoanode, nearly reaching the maximum ( $12.9 \text{ mA cm}^{-2}$ ) of this material, but obvious decay of the photocurrent occurs within 20 minutes.<sup>10,11</sup> In addition, techno-economic analysis demonstrates that the lifetime improvement of the photo(electro)catalytic devices is crucial to make solar hydrogen cost-effective, due to the enhanced efficiency and decreased manufacturing cost of devices with the technical development.<sup>12</sup> Therefore, the stability improvement of photocatalysts/photoelectrodes is challenging yet essential to developing durable devices for practical solar fuel production.

The stability of photocatalysts and photoelectrodes has received much less attention compared with efficiency, as

demonstrated by the number of publications.<sup>13,14</sup> When searching the combined topic 'photocatalytic + stable', 9057 results are presented while the number is 42 153 for 'photocatalytic + efficient' in the database of the Web of Science (08/10/2022). Together with the long feedback loop of stability measurements, the stability improvement experiences slow progress.<sup>15,16</sup> Recently, a  $\sim 3\%$  solar-to-hydrogen conversion efficiency has been reported on a tandem device using  $\text{Cu}_2\text{O}$  as the photocathode and  $\text{BiVO}_4$  as the photoanode, but only 100 h of stability has been demonstrated.<sup>17</sup> Apparently, a 100 h (0.023 years,  $12 \text{ h d}^{-1}$ ) durability of devices is far from the requirement of a five-year lifetime for cost-competitive  $\text{H}_2$  production. Furthermore, the stability issue has been a major concern for some of the most promising candidates, such as metal-organic frameworks and metal halide perovskites.<sup>2,18</sup> Although considerable effort has been devoted to improving the stability of photocatalysts/photoelectrodes, the lack of systematic and reliable stability assessment hinders the progress of stability improvement.<sup>4,19–21</sup> Therefore, the systematic, feasible and reliable procedure for stability appraisal is essential to advance the development of durable devices towards photo(electro)catalytic solar fuel generation.

Although numerous reviews/perspectives related to solar fuel production have been reported, most of them focused on the efficiency or strategies for stability improvement.<sup>1,13,22</sup> Up to date, there is no consensus on the stability evaluation procedure, even though this is a vital practice for the future development of efficient and durable photo(electro)catalytic devices. Here we present a critical discussion to address the stability assessment of heterogeneous photo(electro)catalysts by taking the solar-driven water splitting application as an example. This work begins with a brief introduction of general measurements for the photo(electro)catalytic water splitting. Next, we propose a systematic process to evaluate the stability of photocatalysts and photoelectrodes, and emphasise the purpose of the stability evaluation. A deep understanding of the deactivation mechanisms is critically important for stability improvement. Finally,



*Kazuhiko Maeda is a Professor at the School of Science, Tokyo Institute of Technology. He received his Bachelor's degree from the Tokyo University of Science in 2003 and PhD degree from the University of Tokyo in 2007. Professor Maeda's research focuses on semiconductor photocatalysts that split water to produce hydrogen and oxygen, and metal complex/semiconductor hybrid photo-*

*catalysts that fix carbon dioxide, aiming to achieve highly efficient conversion of sunlight into chemical energy.*



*Gang Liu is a professor and the deputy director of the Institute of Metal Research (IMR), Chinese Academy of Sciences. He received his Bachelor's degree in materials physics from Jilin University in 2003 and PhD degree in materials science from IMR in 2009. Professor Liu's main research interest focuses on solar energy conversion materials and devices for renewable fuels.*



*Lianzhou Wang is an Australian Research Council (ARC) Laureate Fellow and Senior group leader of the Australian Institute for Bioengineering and Nanotechnology (AIBN), Professor at the School of Chemical Engineering, Director of Nanomaterials Centre (Nanomac), The University of Queensland (UQ). He received his PhD degree from the Shanghai Institute of Ceramics,*

*Chinese Academy of Sciences in 1999. Professor Wang's research focuses on the synthesis, characterisation and application of semiconductor nanomaterials for use in renewable energy conversion and storage systems.*



we recommend performing the ‘accelerating test’ for the most promising photocatalysts/photoelectrodes, together with some strategies for stability improvement. This work will initiate the establishment of the feasible and reliable stability assessment of photo(electro)catalysts, and pave the way towards practical solar fuel production.

## 2. Measurement of solar water splitting

Here we introduce general measurements of photocatalytic (PC) and photoelectrochemical (PEC) water splitting, of which the operational conditions are important for the stability assessment. Practical large-scale models of PC and PEC water splitting share similar operational conditions, thus it is valid to transfer the stability assessment conducted in laboratories to industrial applications.<sup>7</sup> It is assumed that readers have the background of the photo(electro) catalysis, especially heterogeneous photo(electro)catalysts for solar energy conversion. The fundamental working mechanisms of the solar-driven photo(electro)catalytic water splitting will not be described in this work. For detailed processes of PC and PEC solar water splitting, we direct readers to some excellent reviews.<sup>23,24</sup>

### 2.1 Photocatalytic (PC) water splitting

Particulate photocatalysts for the PC water splitting are usually composed of light absorbers and co-catalysts for the hydrogen evolution (HER) and/or the oxygen evolution reaction (OER), respectively. A practical model of PC water splitting demonstrated by Domen *et al.* is performed in panel reactors using

photocatalyst sheets (Fig. 1a), which shares the same mechanism as that in the laboratory.<sup>5</sup> Generally, the PC water splitting measurement in the laboratory is conducted in an air-tight reactor with a light window on the topside (Fig. 1b).<sup>25</sup> To begin with, a certain amount of the particulate photocatalyst is dispersed in water and transferred into the reactor. After sealing the reactor and removing the air in the reactor *via* the vacuum pump/gas purge, a solar simulator is put over the top of the reactor as the light source. After lighting on, the HER and OER occur simultaneously on the surface of photocatalysts. Mechanical stirring is usually adopted to keep the suspension of photocatalyst particles. In addition, a thermostat-controlled system (cooling jacket) is necessary to minimise the light-induced temperature fluctuation of the reactor during photocatalytic reactions. The amount of generated H<sub>2</sub> and O<sub>2</sub> is analysed regularly using the gas chromatograph. However, most photocatalysts are not capable of triggering the overall water-splitting reaction due to thermodynamic/kinetic limitations.<sup>26</sup> Half photocatalytic water splitting reactions, namely HER and OER, are usually conducted to evaluate the performance of photocatalysts with the assistance of sacrificial agents (electron donors for HER and electron acceptors for OER (Fig. 1c)).<sup>26</sup> Those photocatalysts can form Z-scheme systems with proper redox couples (*e.g.*, Fe<sup>2+</sup>/Fe<sup>3+</sup>) or solid charge intermedialor (*e.g.*, Au, graphene) to achieve overall water splitting.<sup>27,28</sup> Different from the overall water splitting reaction, H<sub>2</sub> or O<sub>2</sub> is the only product recorded for the photocatalytic HER or OER, respectively. Here the temperature, pressure, pH value of reaction solutions and concentration of sacrificial agents have been demonstrated to influence the efficiency and stability of photocatalysts.<sup>29</sup>

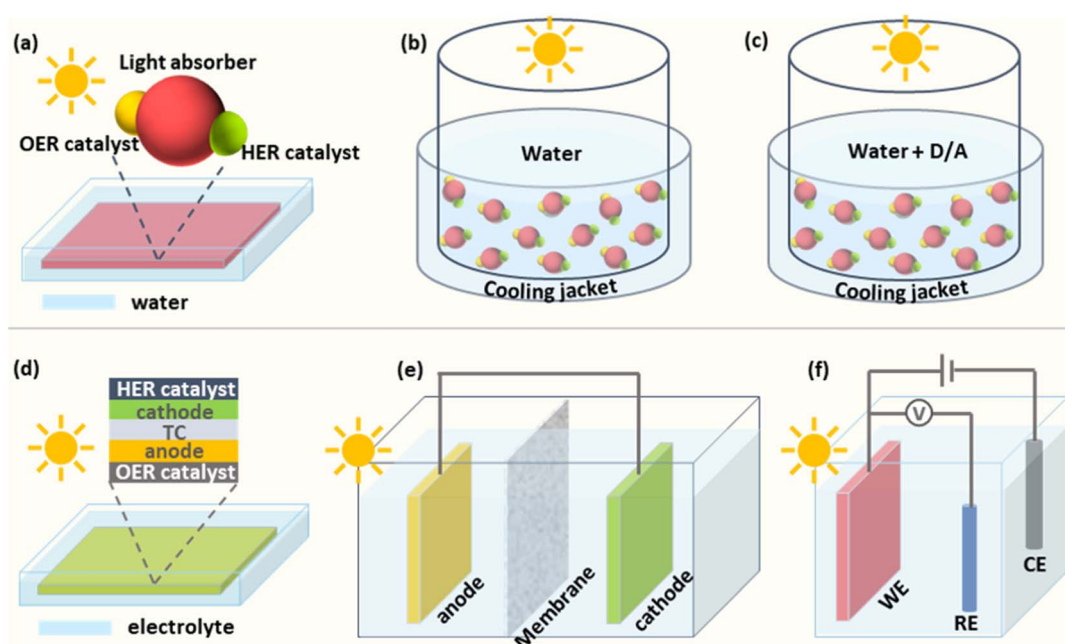


Fig. 1 Solar water splitting systems. (a) The predicted commercial model and (b) the general lab-used model for the PC-based overall water splitting, respectively. (c) Half water splitting. HER: hydrogen evolution reaction, OER: oxygen evolution reaction. D: electron donor, A: electron acceptor. (d) Possible commercial model for the PEC water splitting. (e) Unbiased photoanode-photocathode cell and (f) biased three-electrode cell for the PEC water splitting, respectively. TC: transparent conductor, WE: working electrode, CE: counter electrode, RE: reference electrode.





## 2.2 Photoelectrochemical (PEC) water splitting

The predicted practical model of the PEC water splitting is based on an integrated system, in which the cathode and anode are deposited on two sides of a piece of a transparent conductor (TC) respectively to make an artificial leaf (Fig. 1d).<sup>7,30</sup> Under solar irradiation, H<sub>2</sub> and O<sub>2</sub> are generated from the cathode side and the anode side, respectively. For general single photoanode/photocathode, the light absorber is deposited on a conductive substrate and then co-catalysts for target reactions are loaded on the surface of the light absorber. An ideal PEC water splitting process is that solar-powered HER and OER occur spontaneously on the photocathode and photoanode, respectively (Fig. 1e).<sup>17,30,31</sup> However, it is challenging to match proper photoanodes and photocathodes for unbiased water splitting, thus external bias is applied in most of the case studies.<sup>32</sup> Generally, a three-electrode system is usually used to investigate the performance of single photoelectrodes (Fig. 1f).<sup>33</sup> Taking the photoanode as an example, the photoanode is defined as a working electrode (WE) to run the OER and the HER occurs on the cathode, namely the counter electrode (CE). A fixed area of the photoanode, where a large area (>1 cm<sup>2</sup>) is preferred for practical applications, is exposed to a solar simulator. Different from adding sacrificial agents in PC half-water splitting reactions, the extra bias is applied to provide sufficient potential for the water splitting reaction. Meanwhile, a reference electrode (RE) is applied to calibrate the applied bias. Like all the other electrochemical cells, conductive electrolytes are necessary for the photoelectrochemical cell. Here the temperature and the composition of electrolytes affect the PEC performance significantly.<sup>15</sup>

## 3. Stability evaluation

The definition of 'catalyst' is a substance that alters the rate of a chemical reaction but is itself unchanged at the end of the reaction, according to the Oxford Dictionary. This definition should also apply to photo(electro)catalysts, which are a branch of catalysts.<sup>34</sup> A stable photocatalyst/photoelectrode should work normally under operational conditions without composite changes (crystal structure and chemical formula) during its lifetime. Therefore, the stability assessment should generally include the long-term operating measurement and the characterisation of structural properties of the applied materials after

the durability test. A systematic process for the stability assessment of PC/PEC devices is proposed to advance the reliable report of the stability of photocatalysts and photoelectrodes (Fig. 2). For long-term testing, the stability of photocatalysts/photoelectrodes should be reported by three figures of metrics: run time, operational stability, and material stability. The properties of the catalyst material should be fully characterised, which mainly include morphology, crystal structure, composition, and photoelectronic properties. Additionally, the reaction solution should also be investigated to confirm the operational stability and material stability of photo(electro)catalytic devices. More details will be discussed below.

### 3.1 Long-term testing

**3.1.1 Run time.** When conducting the long-term measurement, the first question is how long the stability test should last. For the practical application of PC and PEC water-splitting systems, at least a five-year lifetime (21 900 h, 12 h d<sup>-1</sup>) is required for photocatalysts/photoelectrodes.<sup>12</sup> A stability test of less than 24 h is usually too short to indicate what may happen to photocatalysts/photoelectrodes after one year, while it is impractical to conduct a five-year measurement. It seems that the photocatalysis community has not reached a consensus on how long the stability test should be performed.<sup>9</sup> A period of at least 100 h is suggested for the early-stage stability assessment, which is time-efficient and feasible in most laboratories.

**3.1.2 Operational condition.** Another important question is the operational conditions for long-term testing. It is well recognised the equal importance of stability and efficiency for water splitting. Operational conditions, such as light intensity, temperature, and loading amount of catalysts, not only influence the solar conversion efficiency but also make a significant impact on the stability of photocatalysts and photoelectrodes, of which the details will be discussed in section 4.2.<sup>29,33</sup> Thus, it is proposed to perform the long-term testing under a standard condition as that proposed for the efficiency evaluation.<sup>35</sup>

**3.1.3 Operational model.** Various kinds of models have been designed to assess the stability of photocatalysts and photoelectrodes. The long-term photocatalytic measurement with continuous light irradiation is a direct way to evaluate the stability of PC water-splitting systems (Fig. 3a).<sup>36–38</sup> However, the accumulation of gas products may result in reverse reactions



Fig. 2 Proposed stability assessment process of photocatalysts/photoelectrodes for solar fuel production.



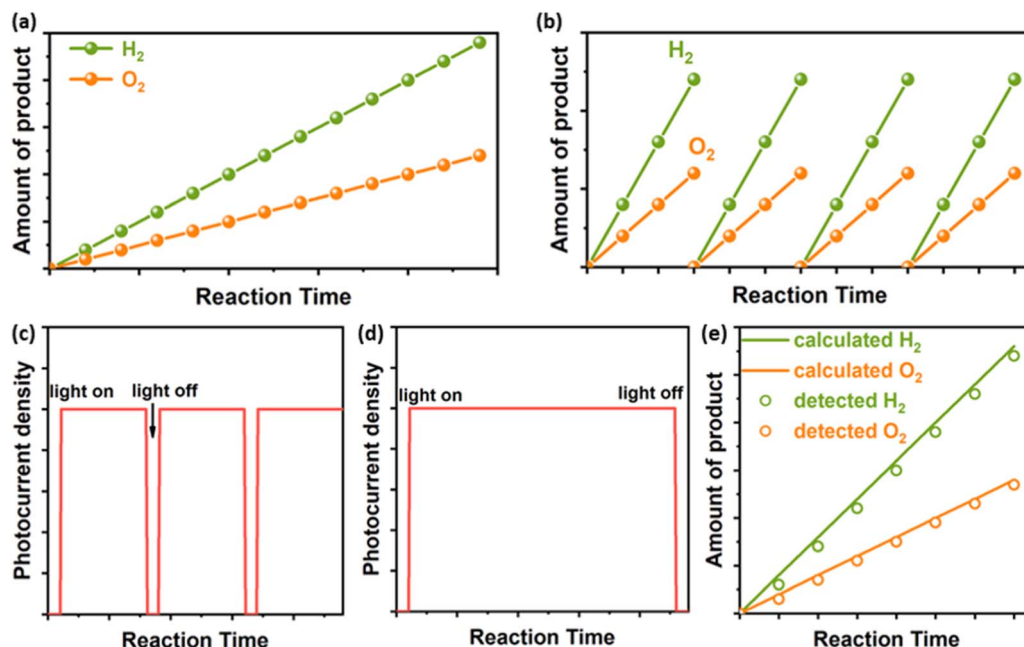


Fig. 3 Schematic models for stability measurement of the PC/PEC water splitting reaction. (a) Continuous and (b) cycling long-term stability tests for the PC water splitting, respectively. (c) Intermittent and (d) continuous  $J$ - $t$  curves of the photoanode in a three-electrode system, respectively. (e) Comparison of detected gas products and calculated gas products from the photocurrent of photoelectrodes.

and impede the water-splitting reaction. Moreover, the consumption of sacrificial agents will lead to a decrease in reaction rate for half-water splitting reactions because an optimal concentration of sacrificial agents usually exists to achieve the highest reaction rate.<sup>39</sup> It is not reasonable to add sacrificial agents during continuous testing because it may be difficult to identify the consumed amount of sacrificial agents. Therefore, the cycling test is more appropriate for PC water-splitting systems (Fig. 3b).<sup>40–42</sup> The continuous test with a certain period is defined as one cycle, and several to tens of cycles can be run using the same photocatalyst. Before starting a new cycle, gas products from the previous cycle can be removed, while photocatalysts can be collected and redispersed in fresh solutions. During the long-term measurement, the  $H_2$  evolution rate and  $O_2$  evolution rate are the major descriptors of stability. The  $H_2/O_2$  evolution rate should keep constant under fixed reaction conditions. As for PEC water splitting systems, the collection of intermittent  $J$ - $t$  curves (Fig. 3c) is preferred rather than continuous  $J$ - $t$  curves (Fig. 3d), because product removal and electrolyte refreshment should also be required during the long-term testing.<sup>43–45</sup> No obvious decrease in photocurrent density usually demonstrates the operational stability of photoelectrodes. In addition, the gas products should be analysed to calculate the Faraday Efficiency (FE) of photoelectrodes (Fig. 3e). A nearly 100% FE indicates an entire utilisation of photogenerated charge carriers in water-splitting reactions, except for  $e^-/h^+$  recombination loss.<sup>9</sup> However, some side reactions may compete with the water splitting reaction, resulting in a less than 100% FE for the photo(electro) catalytic water splitting.<sup>46,47</sup>

### 3.2 Characterisation of photocatalysts/photoelectrodes and reaction solution after testing

Although the constant productivity directly demonstrates the stability of photo(electro)catalytic devices, it may not always reflect the actual stability of photocatalysts/photoelectrodes. If, for example, the self-decomposition of photocatalysts generates the same product as the target catalytic reaction, the initial instability of photocatalysts may be masked in this case.<sup>48</sup> Therefore, the characterisation of catalyst materials and reaction solutions before and after durable testing is necessary to identify the stability of photocatalysts/photoelectrodes.<sup>33</sup> Detailed structure–property relationships are usually investigated before the photocatalytic measurement to understand the mechanisms of unique/excellent performance, while the characterisation of photocatalysts/photoelectrodes after testing is generally oversimplified.<sup>45,49,50</sup> The catalyst materials of a photocatalyst/photoelectrode mainly include a light absorber and co-catalysts for target reactions (HER/OER), which should be investigated after the stability test.<sup>34</sup> A systematic characterisation of the structure and properties of photocatalysts/photoelectrodes should include but not be limited to morphology, crystal structure, composition, and photoelectronic properties. In addition, the reaction solution should also be investigated, which may indicate factors controlling the stability of photocatalysts/photoelectrodes.<sup>51</sup>

**3.2.1 Morphology.** Morphology change usually comes with the degradation of photocatalysts/photoelectrodes.<sup>4</sup> Scanning electron microscopy (SEM) and transmission electron microscopy (TEM) are powerful techniques to ascertain the morphology of photocatalysts/photoelectrodes before and after



PC/PEC reactions. High-resolution SEM and TEM are even ready to identify the local structure of materials at the nanoscale.<sup>52</sup> In particular, the high-resolution TEM can add information on the particle size and distribution of co-catalysts on the surface of light absorbers.<sup>50,53</sup> To evaluate the morphology of the group, the specific surface area of particulate photocatalysts should be measured by using the N<sub>2</sub> adsorption and desorption (Brunauer–Emmett–Teller theory).<sup>54</sup>

**3.2.2 Crystal structure.** X-ray diffraction (XRD) is a typical technique for the characterisation of crystal structures and phases. For photocatalysts/photoelectrodes, the XRD pattern is mainly related to the light absorber.<sup>55</sup> The unchanged XRD patterns of photocatalysts/photoelectrodes before and after PC/PEC measurements usually demonstrate structural stability.<sup>45,54</sup> Catalyst materials with poor crystallinity or even amorphous phase may be characterised using selected-area electron diffraction (SAED) integrated with TEM.<sup>56</sup> The detection of XRD patterns of co-catalysts may be difficult, due to the relatively low loading amount (0.05–5 wt%) and small particle size (>5 nm) of co-catalysts.<sup>57</sup>

**3.2.3 Composition.** Compared to the direct morphology or structural changes, surface reconstruction and the formation of defects more easily occur during the water redox reactions.<sup>58,59</sup> Therefore, the composition of photocatalysts/photoelectrodes, including the element ratio, the chemical state and distribution of all elements should be fully investigated after long-term testing: (1) the inductively coupled plasma atomic emission spectroscopy (ICP-AES), element analysis (EA), and X-ray photoelectron spectroscopy (XPS) are recommended to measure the element ratio of the tested materials;<sup>38,42,58</sup> (2) the X-ray fluorescence (XRF) and energy dispersive spectroscopy (EDS) can collect the details of the element distribution; (3) the combination of Raman spectroscopy and XPS can gain detailed information about the chemical state of elements composed of photocatalysts/photoelectrodes.<sup>60,61</sup>

**3.2.4 Photoelectronic properties.** The light absorption, charge separation and transfer properties of photocatalysts and photoelectrodes play a key role in the photo(electro)catalytic water splitting. On the other hand, the morphology, crystal structure, and composition changes of catalytic materials usually have a significant impact on the photoelectronic properties of photocatalysts and photoelectrodes.<sup>48,62</sup> Hence, the characterisation of photoelectronic properties of photocatalysts and photoelectrodes is indispensable to the stability assessment. UV-vis spectroscopy and photoluminescence (PL) spectroscopy have been generally used to measure the light absorption, charge separation and transfer, and the lifetime of charge carriers of photocatalysts and photoelectrodes, of which the data should be compared before and after the long-term stability test.<sup>11,42,50</sup>

**3.2.5 Reaction solution.** Undesirable side reactions, unbalanced reaction rates between the HER and OER, and the dissolution of photocatalysts/photoelectrodes may change the pH value and composition of reaction solutions during long-term testing.<sup>15</sup> Thus, the investigation of the reaction solution is important to confirm the operational stability and material stability. The ICP-AES and liquid nuclear magnetic resonance

(NMR) can be used to identify the components of the reaction solution, while a pH meter rather than pH test strips is suggested to detect the pH value of the reaction solution accurately.<sup>51</sup>

## 4. Identification of deactivation mechanisms

We define the deactivation of photo(electro)catalytic devices as a 50% decrease in productivity, which refers to classic catalytic systems.<sup>56</sup> The deactivation of photocatalysts and photoelectrodes can be mainly divided into intrinsic instability of catalyst materials and photo/redox-induced instability. Most photo(electro)catalysts investigated show excellent intrinsic stability, thus the identification of deactivation mechanisms will focus on the photo/chemical-induced instability.<sup>13</sup> The photo-generated electrons and holes in semiconducting light absorbers have been demonstrated to possess strong reducing and oxidising potentials, respectively.<sup>34</sup> These electrons and holes may reduce or oxidise the catalyst itself rather than drive the HER or OER, namely photo-corrosion, causing the deactivation of photo(electro)catalytic reactions.<sup>4,8</sup> The photo-corrosion is becoming one of the main challenges in PC and PEC water splitting with the continuous enhancement of efficiency.<sup>42,63,64</sup> As stated by Landsmann *et al.*, 'A general strategy can be applied: identification and analysis of loss mechanisms in photoelectrodes and selection and deposition of specifically designed materials to address these problems.'<sup>65</sup> Therefore, we would like to emphasise the purpose of long-term testing at the early stage of the photo(electro)catalytic technology, which is to find out possible unstable factors rather than demonstrate the stability of targeted materials. Comprehensive characterisations of deactivated photocatalysts and photoelectrodes and a deep understanding of deactivation mechanisms play a key role in guiding the photostability improvement of PC/PEC devices.

### 4.1 Degradation of catalyst materials

The decrease of photocurrent and the H<sub>2</sub>/O<sub>2</sub> evolution rate variation during long-term stability tests are generally derived from the physical and/or chemical changes of photocatalysts/photoelectrodes.<sup>15,51,63</sup> The characterisation of deactivated photocatalysts/photoelectrodes gain a fundamental understanding of deactivation processes under operational conditions. A good model has been demonstrated based on the GaN:ZnO solid solution for PC water splitting.<sup>51</sup>

After studying the effect of reaction conditions on photocatalytic performance, the Rh<sub>2–y</sub>Cr<sub>y</sub>O<sub>3</sub>/GaN:ZnO photocatalyst showed stable water-splitting activity for 3 days (72 h) under optimal reaction conditions.<sup>66</sup> To further investigate the long-term durability of the Rh<sub>2–y</sub>Cr<sub>y</sub>O<sub>3</sub>/GaN:ZnO photocatalyst, the photocatalytic overall water splitting measurement was conducted within 0.5 years.<sup>51</sup> The photocatalysts exhibited stable photocatalytic activity for over 3 months (2160 h) while losing 50% of the initial activity after 6 months (Fig. 4a). Through detailed characterisation of catalysts before and after the





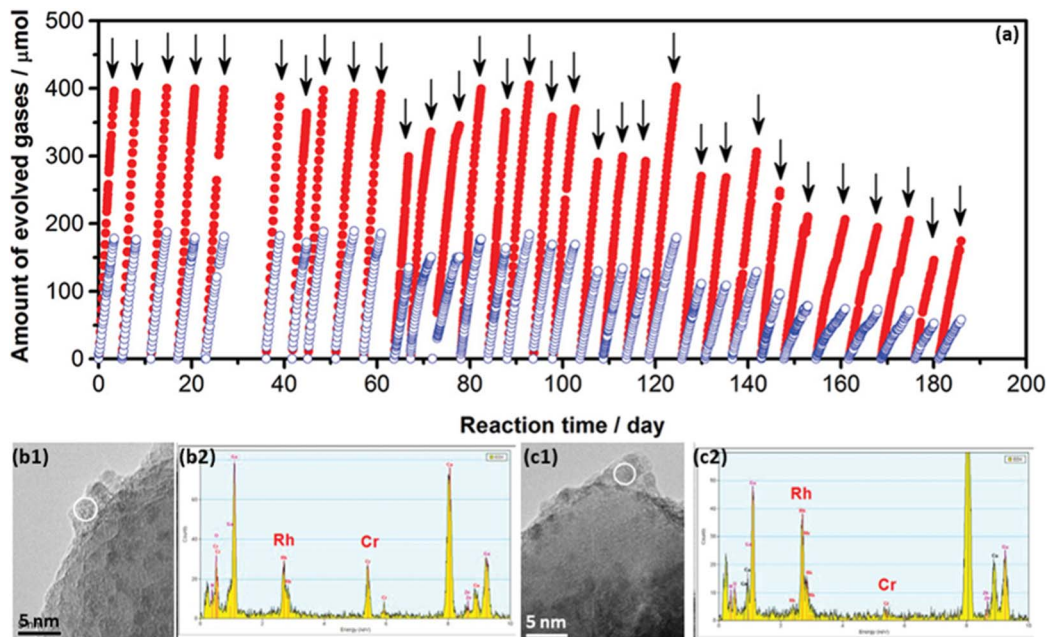


Fig. 4 (a) Long-term measurement of  $\text{Rh}_{2-y}\text{Cr}_y\text{O}_3/\text{GaN}:\text{ZnO}$  photocatalyst for overall water splitting under visible light. (b and c) Combination of TEM and EDS analysis for the  $\text{Rh}_{2-y}\text{Cr}_y\text{O}_3/\text{GaN}$  photocatalyst (b) before and (c) after deactivation. Reproduced from ref. 51, copyright 2012, American Chemical Society.

reaction, the catalyst deactivation was mainly attributed to the collapse of active sites (e.g.,  $\text{Rh}_{2-y}\text{Cr}_y\text{O}_3$ ) for the HER and the oxidation of the nitride component by holes, together with the mechanical damage by stirring the reactant solution (Fig. 4b and c). Meanwhile, “accelerated deactivation” was performed using more intense light, of which the deactivation mechanism was consistent with that of the 6 month deactivation test. Furthermore, possible strategies have been proposed to improve the stability of the  $\text{Rh}_{2-y}\text{Cr}_y\text{O}_3/\text{GaN}:\text{ZnO}$  photocatalyst, such as the reloading of  $\text{Rh}_{2-y}\text{Cr}_y\text{O}_3$  and the co-loading of co-catalysts for the OER to retard the self-oxidation process. Notably, it is suggested to investigate the degradation processes of the material fabricated by different methods, which can find out unstable factors induced by the material synthesis.<sup>67</sup>

General PC/PEC water splitting processes convolve catalytic activities with light absorption and charge transfer, meanwhile, the photocatalyst/photoelectrode is a complex of the light absorber and the co-catalyst.<sup>9,34</sup> The multi-step process and multi-component feature make it challenging to figure out deactivation mechanisms by characterisations of deactivated photocatalysts/photoelectrodes.<sup>68</sup> Therefore, the delicate design of characterisation experiments with the assistance of sophisticated techniques provides a more accurate and thorough understanding of deactivation processes.<sup>20,67</sup> Molybdenum disulfide ( $\text{MoS}_2$ ), with excellent catalytic activity for the HER, is regarded as one of the most promising candidates to replace Pt, while the stability of metal sulphides is a major concern for photocatalytic applications.<sup>69</sup> Atomic force microscopy (AFM) is combined with micro-Raman spectroscopy to reveal the photo-induced degradation of  $\text{MoS}_2$  in fresh water. It is found that edge sites of  $\text{MoS}_2$  flakes are more vulnerable to photo-

corrosion, compared to the basal plane (Fig. 5a and b). More interestingly, the edge sites of single-layer  $\text{MoS}_2$  are demonstrated to be more robust than that of the multi-layer  $\text{MoS}_2$  (Fig. 5c–e). As a result, single-layer  $\text{MoS}_2$  is preferred for PC/PEC water-splitting applications. Another example is the comparison of Ga-terminate and N-terminated GaN nanowires, which identifies the relationship between atomic configuration and the long-term stability of the p-GaN photoelectrode.<sup>70</sup> Sophisticated characterisations clarify the essential role of nitrogen termination in preventing GaN nanowires from (photo)oxidation in air and aqueous electrolyte together with the efficient hole extraction in p-GaN.

Recently, *in situ* or *operando* techniques have been emerging as powerful characterisation methods to complement the understanding of the degradation mechanisms of photocatalysts/photoelectrodes.<sup>67,71,72</sup> Typically, *in situ* electrochemical atomic force microscopy (EC-AFM) is applied to gain more information on the photocorrosion of the  $\text{BiVO}_4$  photoanode. It confirms the film-dissolution-induced degradation and reveals nearly uniform etching on the surface exposed to the electrolyte (Fig. 6a).<sup>67</sup> To further measure the dissolution rate of photoelectrodes in *operando*, the combination of the inductively coupled plasma mass spectrometry (ICP-MS) and an illuminated scanning flow cell (SFC) is designed, which enables time-resolved tracking of the dissolution rate of multiple elements in various kinds of electrolytes (Fig. 6b).<sup>73</sup> Moreover, *in situ* spectroscopies have been demonstrated to identify chemical states of elements, local coordination geometries, and radicals of photocatalysts/photoelectrodes under operational conditions, including diffuse reflectance infrared Fourier-transform spectroscopy (DRIFTS), surface-enhance Raman

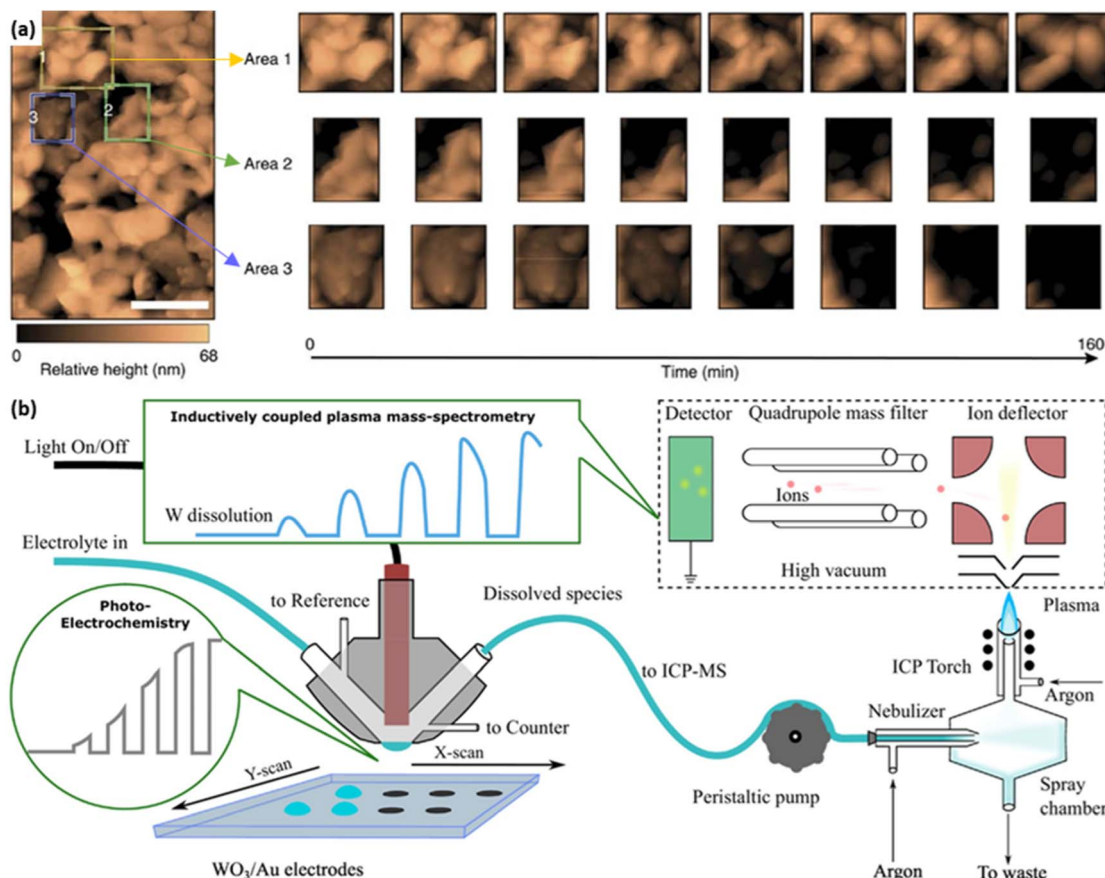




**Fig. 5** (a1 and b1) Optical microscopy (100 $\times$ ) and (a2 and b2) AFM images of exfoliated single- and trilayer flake of MoS<sub>2</sub> on a Si/SiO<sub>2</sub> substrate before (top) and after (bottom) laser line scan immersed in the electrolyte. (c) Optical microscopy image (100 $\times$ ) of exfoliated single- (1L) and trilayer (3L) MoS<sub>2</sub> on a Si/SiO<sub>2</sub> substrate. (d) Monochromatic reflectivity map of before (left) and after (right) a laser scan in the electrolyte of the region of interest (ROI) defined in (c). (e) Raman spectra of the spots marked in (d) of untreated, unaffected, and photodegraded regions. Reprinted with permission from ref. 61, copyright 2015, American Chemical Society.

spectroscopy (SERS), irradiated X-ray photoelectron spectroscopy (XPS), X-ray absorption spectroscopy (XAS), electron paramagnetic resonance (EPR) and so on.<sup>74–78</sup> These *operando*

techniques provide crucial information to recognise the early-state degradation of photocatalysts/photoelectrodes, such as the formation of electronic defects. In addition, computational



**Fig. 6** (a) *In situ* EC-AFM images of the BiVO<sub>4</sub> photoanode. Three coloured boxes represent area 1 (yellow), area 2 (green) and area 3 (blue), of which *operando* scans are recorded in detail. Reprinted with permission from ref. 67, copyright 2016, Nature Publishing Group. (b) Schematic combination of the inductively coupled plasma mass spectrometry (ICP-MS) and the illuminated scan flow cell (SFC). Reprinted with permission from ref. 71, copyright 2018 Elsevier B.V.





methods have been developed to analyse the photocorrosion of photocatalysts/photoelectrodes in recent years.<sup>67</sup> It is important to note that photocatalysts/photoelectrodes should be characterised under conditions related to the practical devices.

For photocatalysts and photoelectrodes, the stability of light absorbers and co-catalysts is usually investigated separately. However, the relationship between the light absorber and the co-catalyst determines that they will affect the stability of each other. The decomposition or dissolution of light absorbers has been demonstrated to loosen the interfacial structure between the light absorber and the co-catalyst or even detach the co-catalyst from the light absorber, resulting in the deactivation of the photo(electro)catalytic activities.<sup>48</sup> On the other hand, the loading of proper co-catalysts on the surface of light absorbers promotes charge separation and accelerates the consumption of charge carriers for the water splitting reaction, which alleviates the charge-carrier-induced photocorrosion of light absorbers.<sup>57</sup> Therefore, evaluating the stability of photocatalysts and photoelectrodes in their entirety is necessary to gain a full picture of the deactivation mechanism.

## 4.2 Impact of the operational environment

The degradation process is the interaction between active materials and environmental stimulations, which mainly include light intensity, O<sub>2</sub>, pressure, reaction solution and temperature for the solar-driven water-splitting reaction.<sup>4</sup> In turn, proper control of the operational environment is possible to stabilise the photocatalysts/photoelectrodes.<sup>15</sup> Thus, environmental stimulations should be analysed together with active materials when investigating the deactivation of photocatalysts and photoelectrodes. Generally, environmental stimulations do not work independently but are affected to a greater or lesser extent by each other (Fig. 7).<sup>20,29,67</sup> The deep understanding of how environmental stimulations influence the stability of catalyst materials is essential to guide the design of durable PC/PEC devices.



Fig. 7 Schematic illustration of the relationship between the photo(electro)catalyst stability and various environmental factors. EC: electrolyte composition.

**4.2.1 Light intensity.** The light intensity has been demonstrated to influence the PC/PEC performance remarkably, which is why a solar simulator with one-sun intensity (AM 1.5G, 100 mW cm<sup>-2</sup>) is recommended to mimic the sunlight irradiation for standard measurements.<sup>35</sup> However, understanding the impact of light intensity on the photo-corrosion of photocatalysts/photoelectrodes is necessary to reveal the deactivation mechanisms. Strong light intensity usually results in fast reaction rates, due to the enhanced number of photo-excited charge carriers. In other words, the high intensity of the light may speed up the photo-corrosion compared to that of sunlight. In addition, ultra-violet (UV) light has been demonstrated to aggravate the decomposition of materials, such as metal halide perovskites.<sup>79</sup>

**4.2.2 O<sub>2</sub>.** O<sub>2</sub> has been demonstrated as an unstable factor for most metal sulphides and metal (oxy)nitrides.<sup>4,61,80</sup> Reactions of O<sub>2</sub> with water and photo-generated electrons/holes result in the formation of reactive oxygen species, including superoxide anion radical, singlet oxygen, hydroxyl radical, and hydrogen peroxide.<sup>81</sup> These reactive oxygen species have been shown to oxidise metal sulphide/nitride materials.<sup>81</sup> The O<sub>2</sub> source mainly includes dissolved O<sub>2</sub> from the air and produced O<sub>2</sub> from the photocatalytic water oxidation reaction.<sup>1</sup> The solubility of O<sub>2</sub> in pure or fresh water is about 9 mg L<sup>-1</sup> at 25 °C, which decreases with the rise of temperature.<sup>82</sup> Proper strategies have been developed to remove the dissolved O<sub>2</sub> from water, while the production of O<sub>2</sub> on the surface of photocatalysts/photoelectrodes seems to be inevitable for the PC/PEC water splitting.<sup>83</sup>

**4.2.3 Pressure.** According to Henry's law, the lower pressure, the lower the H<sub>2</sub>/O<sub>2</sub> solubility in water.<sup>82</sup> An enhanced H<sub>2</sub>/O<sub>2</sub> evolution rate is detected with the decrease of the pressure in the reactor, which is attributed to the fast release of H<sub>2</sub> and O<sub>2</sub> from the aqueous solution and the inhibition of the back reaction between H<sub>2</sub> and O<sub>2</sub>.<sup>1,29</sup> Moreover, the lower pressure results in less dissolved O<sub>2</sub> from the air in water.<sup>82</sup> It seems that a low-pressure environment is preferred for high efficiency and stability. However, the operation of the PC/PEC water splitting under atmosphere pressure should be pursued to minimise the setup and operation costs.

**4.2.4 pH value.** Theoretically, PC and PEC water splitting can be conducted in pure water and neutral aqueous electrolytes, respectively, but it is not always the case. Most photocatalysts and photoelectrodes work at a proper pH range and pH buffers are usually used to maintain the pH values during the PC/PEC water splitting measurement.<sup>63,72,84</sup> The identification of a proper pH range for specific photocatalysts/photoelectrodes is necessary to improve long-term stability.<sup>85,86</sup>

**4.2.5 Electrolyte composition (EC).** The composition of aqueous solutions has a significant impact on the stability of photocatalysts/photoelectrodes.<sup>15,87</sup> The composition engineering of electrolytes has been demonstrated to slow down or even inhibit the photo-corrosion of photocatalysts and photoelectrodes.<sup>15,37</sup> Compared with the PEC water splitting, the composition of aqueous solutions for the PC water splitting has attracted much less attention, which may provide significant influence on the photocatalytic performance.<sup>54,88</sup>



**4.2.6 Temperature.** According to the Arrhenius equation, increased temperature not only promotes target reactions but also accelerates photo-corrosion reactions, and *vice versa*.<sup>55</sup> Meanwhile, the temperature-dependent electron-hole recombination kinetics should be taken into consideration because the increased temperature has been demonstrated to promote non-radiative recombination.<sup>89–91</sup> In addition, the solubility of H<sub>2</sub> and O<sub>2</sub> in water decreases with increasing temperature.<sup>82</sup> Therefore, the proper control of the light-induced heating is required to make a balance between efficiency and stability.

**4.2.7 Others.** In addition to the general environmental stimulations, some factors for specific reactions should also be taken into consideration, such as mechanical stirring, sacrificial agents, and applied bias. Long-term mechanical stirring of the reactant solution has been identified to contribute to the deactivation of PC water splitting by damaging the surface of photocatalysts, which may loosen the contact between light absorbers and co-catalysts, and produce charge recombination centres.<sup>51,92</sup> Therefore, the fabrication of photocatalyst sheets is highly desirable to avoid the impact of mechanical stirring.<sup>29</sup> For half-water splitting reactions, sacrificial agents have shown significant influence on the stability of photocatalysts, which may be attributed to the pH value and the redox potential of different sacrificial agents.<sup>93</sup> The applied bias for PEC water splitting has been demonstrated to be a driving force for the photocorrosion of photoelectrodes, which should be well investigated to understand the deactivation mechanism.<sup>73</sup>

## 5. Conclusion and outlook

The conclusions section should come in this section at the end of the article, before the acknowledgements. The stability challenge of the photo(electro)catalytic devices becomes a major obstacle towards practical solar fuel production. A reliable report of stability results is a prerequisite for the stability improvement of photocatalysts/photoelectrodes. To address the stability challenges effectively, we propose a systematic process for the stability evaluation of photo(electro)catalytic devices, which is expected to advance the reliable evaluation and report of stability results from different laboratories. Furthermore, the purpose of the early-stage stability evaluation is mainly to understand the deactivation mechanisms of photocatalysts/photoelectrodes, which will lay the foundation for the mitigation of unstable issues. Therefore, delicate development and design of experiments and *ex/in situ* techniques are necessary to enable a comprehensive understanding of the deactivation mechanisms of photocatalysts/photoelectrodes. Particular attention should be paid to the impact of the operational conditions on the stability of photo(electro)catalytic devices. This work is expected to initiate wide and intensive debates on stability assessment among the photo(electro)catalysis community, which will ensure continuous and meaningful improvement in this area of research. Further suggestions are proposed to address the stability challenges of photo(electro)catalysts.

The long-term stability assessment is time/resource-consuming, and the long feedback loop impedes the

development of stable photo(electro)catalytic devices towards solar fuel production. Therefore, the long-term stability assessment should be reserved for the most promising catalyst candidates, which have the best combination of stability and efficiency. Another possible strategy is to shorten the feedback loop by running the 'accelerating test', which has been demonstrated by some pioneering works.<sup>79</sup> For instance, the replacement of visible light with intensive UV light speed up the deactivation of the Rh<sub>2–y</sub>Cr<sub>y</sub>O<sub>3</sub>/GaN:ZnO photocatalyst from a period of 4320 h to less than 100 h.<sup>51</sup> Since the mechanisms of deactivation probably are not the same for different photocatalysts/photoelectrodes and are not yet thoroughly understood, it is not clear what acceleration factors are important. Continuous effort is required to clarify the deactivation mechanisms before reliable 'accelerating tests' can be performed.

Based on the understanding of deactivation mechanisms, the ongoing development of effective strategies is required to improve the stability of photocatalysts/photoelectrodes. As discussed in section 4, the photocorrosion of photocatalysts/photoelectrodes is mainly caused by the accumulation of photo-excited charge carriers. Therefore, the fast extraction of photo-generated electrons and holes from active materials should inhibit photocorrosion effectively. Facet engineering is a promising strategy to improve stability, due to the facet-dependent charge separation, catalytic activity, and stability.<sup>94,95</sup> In addition, the electron transfer layer and hole transfer layer in perovskite solar cell devices may be a good reference for charge extraction.<sup>79</sup> Moreover, the delicate design of co-catalysts should be pursued to accelerate water redox reactions and enhance the charge consumption rate.<sup>13</sup> Meanwhile, photo-corrosion mostly involves the contact of active materials with water/electrolyte/O<sub>2</sub>. Thus, surface coating may be a proper strategy to isolate active materials from those unstable factors. With proper coating layers, metal halide perovskites can work as photoelectrodes for water splitting.<sup>96</sup> Facial methods and advanced materials for surface coating are desirable to make durable and cost-effective photo(electro)catalytic devices.<sup>97</sup> If a substantial fraction of the photo(electro)catalysis community continues to address the stability challenges of photo(electro)catalysts, it is believed that the advanced technology of photo(electro)catalytic solar to fuel conversion will emerge much faster.

## Author contributions

L. Wang and M. Xiao designed and directed this perspective. M. Xiao wrote the manuscript. All the authors contributed to the discussion, editing and revision of this work.

## Conflicts of interest

There are conflicts to declare.

## Acknowledgements

The authors acknowledge the support from the Australian Research Council through its Laureate Fellowship project



FL190100139 and Discovery Program DP200101900. K. M. would like to thank the financial support from JSPS KAKENHI (JP22H05148 and JPJSCCA20200004).

## References

- 1 C. Bie, L. Wang and J. Yu, *Chem*, 2022, **8**, 1567–1574.
- 2 X.-S. Wang, L. Li, D. Li and J. Ye, *Sol. RRL*, 2020, **4**, 1900547.
- 3 E. Gong, S. Ali, C. B. Hiragond, H. S. Kim, N. S. Powar, D. Kim, H. Kim and S.-I. In, *Energy Environ. Sci.*, 2022, **15**, 880–937.
- 4 Z. Wang, Y. Gu, L. Zheng, J. Hou, H. Zheng, S. Sun and L. Wang, *Adv. Mater.*, 2022, **34**, 2106776.
- 5 H. Nishiyama, T. Yamada, M. Nakabayashi, Y. Maehara, M. Yamaguchi, Y. Kuromiya, Y. Nagatsuma, H. Tokudome, S. Akiyama, T. Watanabe, R. Narushima, S. Okunaka, N. Shibata, T. Takata, T. Hisatomi and K. Domen, *Nature*, 2021, **598**, 304–307.
- 6 H. Song, S. Luo, H. Huang, B. Deng and J. Ye, *ACS Energy Lett.*, 2022, **7**, 1043–1065.
- 7 B. A. Pinaud, J. D. Benck, L. C. Seitz, A. J. Forman, Z. Chen, T. G. Deutsch, B. D. James, K. N. Baum, G. N. Baum, S. Ardo, H. Wang, E. Miller and T. F. Jaramillo, *Energy Environ. Sci.*, 2013, **6**, 1983–2002.
- 8 J. Su, Y. Wei and L. Vayssieres, *J. Phys. Chem. Lett.*, 2017, **8**, 5228–5238.
- 9 J. H. Kim, D. Hansora, P. Sharma, J.-W. Jang and J. S. Lee, *Chem. Soc. Rev.*, 2019, **48**, 1908–1971.
- 10 G. Liu, S. Ye, P. Yan, F. Xiong, P. Fu, Z. Wang, Z. Chen, J. Shi and C. Li, *Energy Environ. Sci.*, 2016, **9**, 1327–1334.
- 11 J. Fu, Z. Fan, M. Nakabayashi, H. Ju, N. Pastukhova, Y. Xiao, C. Feng, N. Shibata, K. Domen and Y. Li, *Nat. Commun.*, 2022, **13**, 729.
- 12 J. Schneidewind, *Adv. Energy Mater.*, 2022, **12**, 2200342.
- 13 X. Tao, Y. Zhao, S. Wang, C. Li and R. Li, *Chem. Soc. Rev.*, 2022, **51**, 3561–3608.
- 14 D. K. Lee, D. Lee, M. A. Lumley and K.-S. Choi, *Chem. Soc. Rev.*, 2019, **48**, 2126–2157.
- 15 D. K. Lee and K.-S. Choi, *Nat. Energy*, 2018, **3**, 53–60.
- 16 J.-B. Pan, B.-H. Wang, J.-B. Wang, H.-Z. Ding, W. Zhou, X. Liu, J.-R. Zhang, S. Shen, J.-K. Guo, L. Chen, C.-T. Au, L.-L. Jiang and S.-F. Yin, *Angew. Chem., Int. Ed.*, 2021, **60**, 1433–1440.
- 17 L. Pan, J. H. Kim, M. T. Mayer, M.-K. Son, A. Ummadisingu, J. S. Lee, A. Hagfeldt, J. Luo and M. Grätzel, *Nat. Catal.*, 2018, **1**, 412–420.
- 18 H. Huang, B. Pradhan, J. Hofkens, M. B. J. Roeflaers and J. A. Steele, *ACS Energy Lett.*, 2020, **5**, 1107–1123.
- 19 N. Pastukhova, A. Mavrič and Y. Li, *Adv. Mater. Interfaces*, 2021, **8**, 2002100.
- 20 G. F. Samu and C. Janáky, *J. Am. Chem. Soc.*, 2020, **142**, 21595–21614.
- 21 J.-B. Pan, S. Shen, L. Chen, C.-T. Au and S.-F. Yin, *Adv. Funct. Mater.*, 2021, **31**, 2104269.
- 22 E. Zhao, K. Du, P.-F. Yin, J. Ran, J. Mao, T. Ling and S.-Z. Qiao, *Adv. Sci.*, 2022, **9**, 2104363.
- 23 S. Chen, T. Takata and K. Domen, *Nat. Rev. Mater.*, 2017, **2**, 17050.
- 24 T. Hisatomi, J. Kubota and K. Domen, *Chem. Soc. Rev.*, 2014, **43**, 7520–7535.
- 25 T. Takata, C. Pan and K. Domen, *Sci. Technol. Adv. Mater.*, 2015, **16**, 033506.
- 26 M. Xiao, Z. Wang, M. Lyu, B. Luo, S. Wang, G. Liu, H.-M. Cheng and L. Wang, *Adv. Mater.*, 2019, **31**, 1801369.
- 27 P. Zhou, J. Yu and M. Jaroniec, *Adv. Mater.*, 2014, **26**, 4920–4935.
- 28 J. Low, C. Jiang, B. Cheng, S. Wageh, A. A. Al-Ghamdi and J. Yu, *Small Methods*, 2017, **1**, 1700080.
- 29 Q. Wang, T. Hisatomi, Q. Jia, H. Tokudome, M. Zhong, C. Wang, Z. Pan, T. Takata, M. Nakabayashi, N. Shibata, Y. Li, I. D. Sharp, A. Kudo, T. Yamada and K. Domen, *Nat. Mater.*, 2016, **15**, 611–615.
- 30 D. G. Nocera, *Acc. Chem. Res.*, 2012, **45**, 767–776.
- 31 Z. Luo, T. Wang and J. Gong, *Chem. Soc. Rev.*, 2019, **48**, 2158–2181.
- 32 W. Yang, R. R. Prabhakar, J. Tan, S. D. Tilley and J. Moon, *Chem. Soc. Rev.*, 2019, **48**, 4979–5015.
- 33 Z. Chen, T. G. Deutsch, H. N. Dinh, K. Domen, K. Emery, A. J. Forman, N. Gaillard, R. Garland, C. Heske, T. F. Jaramillo, A. Kleiman-Shwarscstein, E. Miller, K. Takanabe and J. Turner, in *Photoelectrochemical Water Splitting: Standards, Experimental Methods, and Protocols*, ed. Z. Chen, H. N. Dinh and E. Miller, Springer New York, New York, NY, 2013, pp. 17–44, DOI: [10.1007/978-1-4614-8298-7\\_3](https://doi.org/10.1007/978-1-4614-8298-7_3).
- 34 A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253–278.
- 35 Z. Wang, T. Hisatomi, R. Li, K. Sayama, G. Liu, K. Domen, C. Li and L. Wang, *Joule*, 2021, **5**, 344–359.
- 36 X. Zhao, S. Chen, H. Yin, S. Jiang, K. Zhao, J. Kang, P. F. Liu, L. Jiang, Z. Zhu, D. Cui, P. Liu, X. Han, H. G. Yang and H. Zhao, *Matter*, 2020, **3**, 935–949.
- 37 S. Park, W. J. Chang, C. W. Lee, S. Park, H.-Y. Ahn and K. T. Nam, *Nat. Energy*, 2016, **2**, 16185.
- 38 L. Lin, Z. Lin, J. Zhang, X. Cai, W. Lin, Z. Yu and X. Wang, *Nat. Catal.*, 2020, **3**, 649–655.
- 39 M. Liu, Y. Chen, J. Su, J. Shi, X. Wang and L. Guo, *Nat. Energy*, 2016, **1**, 16151.
- 40 T. Takata, J. Jiang, Y. Sakata, M. Nakabayashi, N. Shibata, V. Nandal, K. Seki, T. Hisatomi and K. Domen, *Nature*, 2020, **581**, 411–414.
- 41 Y. Zhang, Z. Sun, Z. Wang, Y. Zang and X. Tao, *Int. J. Hydrogen Energy*, 2022, **47**, 8829–8840.
- 42 D. Zhao, Y. Wang, C.-L. Dong, Y.-C. Huang, J. Chen, F. Xue, S. Shen and L. Guo, *Nat. Energy*, 2021, **6**, 388–397.
- 43 Y. Xiao, C. Feng, J. Fu, F. Wang, C. Li, V. F. Kunzelmann, C.-M. Jiang, M. Nakabayashi, N. Shibata, I. D. Sharp, K. Domen and Y. Li, *Nat. Catal.*, 2020, **3**, 932–940.
- 44 S. Wang, P. Chen, Y. Bai, J.-H. Yun, G. Liu and L. Wang, *Adv. Mater.*, 2018, **30**, 1800486.
- 45 S. Wang, T. He, P. Chen, A. Du, K. Ostrikov, W. Huang and L. Wang, *Adv. Mater.*, 2020, **32**, 2001385.
- 46 Q. Mi, A. Zhanaidarova, B. S. Brunshwig, H. B. Gray and N. S. Lewis, *Energy Environ. Sci.*, 2012, **5**, 5694–5700.





- 47 W. Kim, T. Tachikawa, D. Monllor-Satoca, H.-i. Kim, T. Majima and W. Choi, *Energy Environ. Sci.*, 2013, **6**, 3732–3739.
- 48 P. Chen, X. a. Dong, M. Huang, K. Li, L. Xiao, J. Sheng, S. Chen, Y. Zhou and F. Dong, *ACS Catal.*, 2022, **12**, 4560–4570.
- 49 M. Liu, C. Wei, H. Zhuzhang, J. Zhou, Z. Pan, W. Lin, Z. Yu, G. Zhang and X. Wang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202113389.
- 50 P. Zhou, H. Chen, Y. Chao, Q. Zhang, W. Zhang, F. Lv, L. Gu, Q. Zhao, N. Wang, J. Wang and S. Guo, *Nat. Commun.*, 2021, **12**, 4412.
- 51 T. Ohno, L. Bai, T. Hisatomi, K. Maeda and K. Domen, *J. Am. Chem. Soc.*, 2012, **134**, 8254–8259.
- 52 W. Yuan, B. Zhu, X.-Y. Li, T. W. Hansen, Y. Ou, K. Fang, H. Yang, Z. Zhang, J. B. Wagner, Y. Gao and Y. Wang, *Science*, 2020, **367**, 428–430.
- 53 I. Tsuji, H. Kato, H. Kobayashi and A. Kudo, *J. Am. Chem. Soc.*, 2004, **126**, 13406–13413.
- 54 G. Zhang, L. Lin, G. Li, Y. Zhang, A. Savateev, S. Zafeiratos, X. Wang and M. Antonietti, *Angew. Chem., Int. Ed.*, 2018, **57**, 9372–9376.
- 55 S. Cao, Y. Chen, H. Wang, J. Chen, X. Shi, H. Li, P. Cheng, X. Liu, M. Liu and L. Piao, *Joule*, 2018, **2**, 549–557.
- 56 C. Spöri, J. T. H. Kwan, A. Bonakdarpour, D. P. Wilkinson and P. Strasser, *Angew. Chem., Int. Ed.*, 2017, **56**, 5994–6021.
- 57 X. Li, J. Yu, M. Jaroniec and X. Chen, *Chem. Rev.*, 2019, **119**, 3962–4179.
- 58 H. Chai, P. Wang, T. Wang, L. Gao, F. Li and J. Jin, *ACS Appl. Mater. Interfaces*, 2021, **13**, 47572–47580.
- 59 M. Matsukawa, R. Ishikawa, T. Hisatomi, Y. Moriya, N. Shibata, J. Kubota, Y. Ikuhara and K. Domen, *Nano Lett.*, 2014, **14**, 1038–1041.
- 60 Q. Guo, C. Zhou, Z. Ma, Z. Ren, H. Fan and X. Yang, *Chem. Soc. Rev.*, 2016, **45**, 3701–3730.
- 61 E. Parzinger, B. Miller, B. Blaschke, J. A. Garrido, J. W. Ager, A. Holleitner and U. Wurstbauer, *ACS Nano*, 2015, **9**, 11302–11309.
- 62 T. Lange, S. Reichenberger, M. Rohe, M. Bartsch, L. Kampermann, J. Klein, J. Strunk, G. Bacher, R. Schlögl and S. Barcikowski, *Adv. Funct. Mater.*, 2021, **31**, 2009323.
- 63 Q. Wang, M. Nakabayashi, T. Hisatomi, S. Sun, S. Akiyama, Z. Wang, Z. Pan, X. Xiao, T. Watanabe, T. Yamada, N. Shibata, T. Takata and K. Domen, *Nat. Mater.*, 2019, **18**, 827–832.
- 64 Z. Wang, Y. Inoue, T. Hisatomi, R. Ishikawa, Q. Wang, T. Takata, S. Chen, N. Shibata, Y. Ikuhara and K. Domen, *Nat. Catal.*, 2018, **1**, 756–763.
- 65 S. Landsmann, Y. Surace, M. Trottmann, S. Dilger, A. Weidenkaff and S. Pokrant, *ACS Appl. Mater. Interfaces*, 2016, **8**, 12149–12157.
- 66 K. Maeda, K. Teramura, H. Masuda, T. Takata, N. Saito, Y. Inoue and K. Domen, *J. Phys. Chem. B*, 2006, **110**, 13107–13112.
- 67 F. M. Toma, J. K. Cooper, V. Kunzelmann, M. T. McDowell, J. Yu, D. M. Larson, N. J. Borys, C. Abelyan, J. W. Beeman, K. M. Yu, J. Yang, L. Chen, M. R. Shaner, J. Spurgeon, F. A. Houle, K. A. Persson and I. D. Sharp, *Nat. Commun.*, 2016, **7**, 12012.
- 68 S. Cao and L. Piao, *Angew. Chem., Int. Ed.*, 2020, **59**, 18312–18320.
- 69 C. Wu, J. Zhang, X. Tong, P. Yu, J.-Y. Xu, J. Wu, Z. M. Wang, J. Lou and Y.-L. Chueh, *Small*, 2019, **15**, 1900578.
- 70 M. G. Kibria, R. Qiao, W. Yang, I. Boukahil, X. Kong, F. A. Chowdhury, M. L. Trudeau, W. Ji, H. Guo, F. J. Himpsel, L. Vayssieres and Z. Mi, *Adv. Mater.*, 2016, **28**, 8388–8397.
- 71 J. Knöppel, S. Zhang, F. D. Speck, K. J. J. Mayrhofer, C. Scheu and S. Cherevko, *Electrochem. Commun.*, 2018, **96**, 53–56.
- 72 S. Zhang, I. Ahmet, S.-H. Kim, O. Kasian, A. M. Mingers, P. Schnell, M. Kölbach, J. Lim, A. Fischer, K. J. J. Mayrhofer, S. Cherevko, B. Gault, R. van de Krol and C. Scheu, *ACS Appl. Energy Mater.*, 2020, **3**, 9523–9527.
- 73 S. Zhang, M. Rohloff, O. Kasian, A. M. Mingers, K. J. J. Mayrhofer, A. Fischer, C. Scheu and S. Cherevko, *J. Phys. Chem. C*, 2019, **123**, 23410–23418.
- 74 L. Yuan, S.-F. Hung, Z.-R. Tang, H. M. Chen, Y. Xiong and Y.-J. Xu, *ACS Catal.*, 2019, **9**, 4824–4833.
- 75 Y. Hu, F. Zhan, Q. Wang, Y. Sun, C. Yu, X. Zhao, H. Wang, R. Long, G. Zhang, C. Gao, W. Zhang, J. Jiang, Y. Tao and Y. Xiong, *J. Am. Chem. Soc.*, 2020, **142**, 5618–5626.
- 76 L. Wang, B. Cheng, L. Zhang and J. Yu, *Small*, 2021, **17**, 2103447.
- 77 F. Liu, N. Feng, Q. Wang, J. Xu, G. Qi, C. Wang and F. Deng, *J. Am. Chem. Soc.*, 2017, **139**, 10020–10028.
- 78 S. A. Bonke, T. Risse, A. Schnegg and A. Brückner, *Nat. Rev. Methods Primers*, 2021, **1**, 33.
- 79 C. C. Boyd, R. Checharoen, T. Leijtsens and M. D. McGehee, *Chem. Rev.*, 2019, **119**, 3418–3451.
- 80 J. Xiao, Q. Han, Y. Xie, J. Yang, Q. Su, Y. Chen and H. Cao, *Environ. Sci. Technol.*, 2017, **51**, 13380–13387.
- 81 Y. Nosaka and A. Y. Nosaka, *Chem. Rev.*, 2017, **117**, 11302–11336.
- 82 N. I. Kolev, in *Multiphase Flow Dynamics 4: Turbulence, Gas Adsorption and Release, Diesel Fuel Properties*, ed. N. I. Kolev, Springer Berlin Heidelberg, Berlin, Heidelberg, 2012, pp. 209–239, DOI: [10.1007/978-3-642-20749-5\\_11](https://doi.org/10.1007/978-3-642-20749-5_11).
- 83 X. Ning and G. Lu, *Nanoscale*, 2020, **12**, 1213–1223.
- 84 M. Sarnowska, K. Bienkowski, P. J. Barczuk, R. Solarska and J. Augustynski, *Adv. Energy Mater.*, 2016, **6**, 1600526.
- 85 Y.-D. Wang, T.-W. Lee, Y.-C. Lo, W.-J. Hong and C. Chen, *Carbon*, 2021, **175**, 223–232.
- 86 Y. Yang, Y. Ling, G. Wang, T. Liu, F. Wang, T. Zhai, Y. Tong and Y. Li, *Nano Lett.*, 2015, **15**, 7051–7057.
- 87 C.-F. Liu, Y.-J. Lu and C.-C. Hu, *ACS Omega*, 2018, **3**, 3429–3439.
- 88 G. Zhang, G. Li, T. Heil, S. Zafeiratos, F. Lai, A. Savateev, M. Antonietti and X. Wang, *Angew. Chem., Int. Ed.*, 2019, **58**, 3433–3437.
- 89 E. M. Hutter and T. J. Savenije, *ACS Energy Lett.*, 2018, **3**, 2068–2069.
- 90 L. Hultdt, N. G. Nilsson and K. G. Svantesson, *Appl. Phys. Lett.*, 1979, **35**, 776–777.



- 91 R. Scott, S. Kickhöfel, O. Schoeps, A. Antanovich, A. Prudnikau, A. Chuvilin, U. Woggon, M. Artemyev and A. W. Achtstein, *Phys. Chem. Chem. Phys.*, 2016, **18**, 3197–3203.
- 92 M. Matsumura, S. Furukawa, Y. Saho and H. Tsubomura, *J. Phys. Chem.*, 1985, **89**, 1327–1329.
- 93 M. J. Berr, P. Wagner, S. Fischbach, A. Vaneski, J. Schneider, A. S. Susa, A. L. Rogach, F. Jäckel and J. Feldmann, *Appl. Phys. Lett.*, 2012, **100**, 223903.
- 94 H. L. Tan, X. Wen, R. Amal and Y. H. Ng, *J. Phys. Chem. Lett.*, 2016, **7**, 1400–1405.
- 95 S. Wang, G. Liu and L. Wang, *Chem. Rev.*, 2019, **119**, 5192–5247.
- 96 I. Poli, U. Hintermair, M. Regue, S. Kumar, E. V. Sackville, J. Baker, T. M. Watson, S. Eslava and P. J. Cameron, *Nat. Commun.*, 2019, **10**, 2097.
- 97 J. Tan, B. Kang, K. Kim, D. Kang, H. Lee, S. Ma, G. Jang, H. Lee and J. Moon, *Nat. Energy*, 2022, **7**, 537–547.

