Chemical Science



EDGE ARTICLE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2023, 14, 7475

dll publication charges for this article have been paid for by the Royal Society of Chemistry

Received 27th March 2023 Accepted 17th May 2023

DOI: 10.1039/d3sc01591b

rsc.li/chemical-science

Direct mechanocatalysis by resonant acoustic mixing (RAM)†

Cameron B. Lennox, (1) ab Tristan H. Borchers, ab Lori Gonnet, (1) ab Christopher J. Barrett, (1) b Stefan G. Koenig, (1) *C Karthik Nagapudi (1) *C and Tomislav Friščić (1) *ab

We demonstrate the use of a metal surface to directly catalyse copper-catalysed alkyne-azide click-coupling (CuAAC) reactions under the conditions of Resonant Acoustic Mixing (RAM) – a recently introduced and scalable mechanochemical methodology that uniquely eliminates the need for bulk solvent, as well as milling media. By using a simple copper coil as a catalyst, this work shows that direct mechanocatalysis can occur in an impact-free environment, relying solely on high-speed mixing of reagents against a metal surface, without the need for specially designed milling containers and media. By introducing an experimental setup that enables real-time Raman spectroscopy monitoring of RAM processes, we demonstrate 0th-order reaction kinetics for several selected CuAAC reactions, supporting surface-based catalysis. The herein presented RAM-based direct mechanocatalysis methodology is simple, enables the effective one-pot, two-step synthesis of triazoles *via* a combination of benzyl azide formation and CuAAC reactions on a wide scope of reagents, provides control over reaction stoichiometry that is herein shown to be superior to that seen in solution or by using more conventional CuCl catalyst, and is applied for simple gram-scale synthesis of the anticonvulsant drug Rufinamide.

Mechanochemistry is a versatile synthetic approach which¹⁻⁴ avoids the need for bulk solvents, making it intrinsically more green and environmentally-friendly,5,6 and can offer access to reactions and products otherwise difficult to achieve.^{7,8} While mechanosynthesis traditionally relies on impact and mixing resulting from the use of balls or screws, Resonant Acoustic Mixing (RAM, Fig. 1a-c)9,10 has recently emerged as a strategy to conduct mechanochemical reactions without such milling or crushing media. Instead, RAM achieves reactivity by shaking materials at a low acoustic frequency (e.g., 60 Hz), with energy input modulated through changes in the vertical acceleration of the reaction vessel (0–100 g, where $g = 9.81 \text{ m s}^{-2}$). By avoiding the need for milling media, RAM enables simplification of reaction design, avoids product contamination resulting from chipping and abrasion, and facilitates scale-up. So far, RAM has been shown to enable a simple, efficient, and rapid approach to metal-organic frameworks, cocrystals, mechano-redox catalysis, as well as several metal-catalyzed transformations. 11

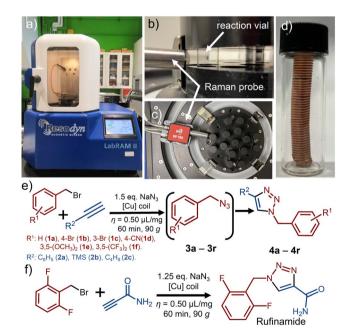


Fig. 1 (a) The LabRAM II instrument used in this work; (b) side-view of the custom-made LabRAM II sample holder with a cut-out to accommodate the Raman probe spectroscopy and (c) top-view of the holder enabling the use of commercial sample vials as reaction vessels, and (d) a typical copper coil used for direct mechanocatalysis by RAM. Reaction scheme for herein developed: (e) model RAM direct mechanocatalysis reactions and (f) RAM direct mechanocatalysis reaction leading to the API Rufinamide. The η -value is the ratio of liquid additive volume (μ L) and weight of reagents (mg).

[&]quot;School of Chemistry, University of Birmingham, Birmingham, B15 2TT, UK. E-mail: t.friscic@bham.ac.uk

^bDepartment of Chemistry, McGill University, 801 Sherbrooke St. W., Montreal, Quebec, H3H 0B8, Canada

Small Molecule Pharmaceutical Sciences, Genentech Inc., One DNA Way, South San Francisco, CA, 94080, USA

[†] Electronic supplementary information (ESI) available. CCDC 2223762. For ESI and crystallographic data in CIF or other electronic format see DOI: https://doi.org/10.1039/d3sc01591b

An exciting emergent opportunity in ball-milling mechanochemistry is direct mechanocatalysis, where components of the milling assembly itself (*e.g.*, balls and/or vessel walls) acts as the metal catalyst.^{12–17} This methodology, pioneered by the Mack and Borchardt groups, has so far been applied to several copper-, palladium-, silver- or nickel-based transformations.^{8b,12,15,18–20} The key advantages of direct mechanocatalysis are straightforward introduction, removal, and reusability of metal catalyst, as well as simplicity of product recovery, but the methodology is challenged by the need to manufacture specialised ball-milling equipment.

As direct mechanocatalysis involves dynamic contact between the reaction mixture and a metal, we speculated it should be compatible with RAM, potentially offering an even simpler, more efficient synthesis by bringing into contact the reaction mixture and a metal surface, without the need to design specialised equipment or generate impact by using milling media.

Here, we provide a proof-of-principle demonstration of direct mechanocatalysis by RAM, focusing on the coppercatalyzed alkyne-azide click-coupling (CuAAC) as a model reaction. RAM enabled a surprisingly uncomplicated approach to direct mechanocatalysis, replacing custom-made milling equipment with simple copper wire. This straightforward reaction platform allowed fast (≤60 minutes) direct mechanocatalysis, without copper-based milling media or vessels ubiquitous in previous examples of copper-based direct mechanocatalysis. While the herein developed process is applicable to a range of solid or liquid benzyl bromide and alkyne reactants, we also show that it permits selective mono- or bis-derivatization, as well as desymmetrization of a symmetrical dialkyne reactant, and is readily scalable to at least one gram, as demonstrated in the RAM synthesis of the anticonvulsant API Rufinamide.

As the model reaction we used the one-pot, two-step reaction of benzyl bromide (1a) and phenylacetylene (2a) in the presence of 1.5 equivalents (50% excess) of NaN3. The reaction is expected to proceed via the intermediate benzyl azide (3a) to form the click coupling product 4a (Fig. 1e). As the catalyst, we used a piece of copper wire of 0.9 mm diameter (#20-gauge), wound into a coil of 45 mm imes 10 mm dimensions. The coil was wedged between the vial cap and the bottom of the vial, preventing it from moving during mixing. The reaction was conducted by RAM in the presence of a liquid additive, with the ratio of the volume of liquid additive to the weight of reaction mixture $\eta =$ 0.50 µL mg⁻¹. As the liquid additive, we explored dimethylsulfoxide (DMSO), water, methanol (MeOH), and a 1:1 by volume mixture of water and DMSO, among which DMSO alone was found to be the most effective. While the initial attempt of reaction gave 4a in conversion below 4 \pm 3% after 60 minutes (Table 1, Entry 2), subsequent attempts using the same copper coil gave 4a quantitatively within 60 minutes (Fig. 2a, Table 1, Entry 3, also ESI†).

Similar behaviour was observed when the reaction was conducted using 20 minute cycles: improvement in reactivity was seen only after the third cycle (Fig. 2a, also ESI \dagger). Overall, these observations indicate an induction period of *ca*.

60 minutes, after which the copper coil becomes a highly effective catalyst. For comparison, the analogous one-pot reaction using either CuCl or copper(II) acetate monohydrate as the catalyst (3 mol% relative to 1a) gave no more than 30% conversion after 60 minutes of RAM (Table 1, Entries 4 and 5, and ESI†). Using either MeOH or water as a liquid additive led to maximum conversions of ca. 80% and 30% at η -value of 0.50 μ L mg $^{-1}$, respectively, while the mixture of water and DMSO led to conversions below 10% in all cases (see ESI†).

Using a piece of uncoiled copper wire (45 mm length, diameter 0.9 mm, #20-gauge) gave significantly lower conversion to 4a ($24 \pm 4\%$), indicating the importance of metal surface. We also explored the potential effect of atmosphere on this direct RAM mechanocatalysis procedure, revealing only $13 \pm 4\%$ conversion under an argon atmosphere after 60 minutes, while conducting the same reaction in an O_2 atmosphere led to complete conversion to 4a. No product arising from a Glaser-type homocoupling was ever observed. X-ray photoelectron spectroscopy (XPS) on a copper coil before and immediately after a 60 minute RAM reaction revealed the appearance Cu(i) after RAM, which upon exposure to air further oxidized to Cu(i). We conclude that the process of activating the copper coil is related to the formation of Cu(i) species on the surface, which requires the presence of oxygen (see ESI†).

Next, we investigated the possibility to deliberately activate the copper coil through different treatments (Table 1, Entries 6-12). Considering that cleaning the metal surface might play a role, we investigated RAM in the presence of abrasive Celite, which did not improve reactivity in the first cycle. Using SiO2 as the additive, however, led to 36 \pm 2% conversion. We also explored the effect of soaking a fresh copper coil in 2a for 24 h before use, with little improvement on reactivity. However, soaking in 2a in a coil that had previously been treated with SiO₂ led to quantitative conversion. Indeed, quantitative conversion to 4a was achieved by RAM within 60 minutes, by using a coil that has been primed by RAM in the presence of SiO2 and 2a for 60 minutes at 90 g. This priming procedure resulted in a Cu(1)containing surface, as observed by XPS, suggesting that the induction period involves a surface-cleaning process and oxidation to an activated, likely copper(1)-acetylide, layer. Importantly, if the copper coil is stored in an inert Ar atmosphere immediately after activation, it remains catalytically active for at least two weeks. However, if stored in air, the coil loses catalytic activity within 24 hours and needs to be reactivated. This also indicates that coil activation involves the formation of surface Cu(1) species.

To investigate whether coil activation and reaction conversion might be related to leaching of copper from the coil, the conversion to 4a and any changes to the weight of the coil were measured over a set of 10 sequential 60 minutes reaction cycles. The analysis was performed for four separate copper coils, amounting to a total of 40 experiments, which revealed an average copper loss of $0.9 \text{ mol} \pm 0.3\%$ (relative to 2a) in each reaction cycle (Fig. 2a, also ESI†). For each of the four coils, we also verified the amount of copper leached in the third cycle by inductively coupled plasma mass spectrometry (ICP-MS), revealing a loss of 0.81 mol%, consistent with the value

Table 1 Conversions for the RAM reaction between 1a, 2a and NaN₃^a

Entry	Copper source	Copper treatment	Conversion ^b (%)
1	_	n/a	0
2	Cu coil	n/a	4 ± 3
3	Cu coil	1a, 2a, NaN ₃ ^a	>95
4	CuCl^c	n/a	31 ± 4
5	$Cu(OAc)_2 \cdot H_2O^c$	n/a	26 ± 6
6	Cu coil	Celite	6 ± 1
7	Cu coil	$\mathrm{SiO_2}^d$	36 ± 2
8	Cu coil	$2a^e$	14 ± 6
9	Cu coil	SiO_2^d followed by $2a^e$	>95
10	Cu coil	2a and SiO_2^f	>95
11	Cu coil	125 °C for 24 h	34 ± 2
12	Cu coil	CH₃COOH ^e followed by 125 °C for 24 h	68 ± 1
13	Cu coil	1a , 2a , NaN ₃ ^{a,g}	>95 ^g

^a Reactions conducted by RAM of equimolar (2 mmol) amounts of **1a** and **2a** with 1.5 equivalents of NaN₃, and DMSO ($\eta = 0.50 \,\mu\text{L mg}^{-1}$) at 90 g for 60 minutes. ^b Based on triplicate experiments and ¹H NMR analysis following dissolution of the entire reaction mixture in CDCl₃. ^c RAM of equimolar amounts of **1a** and **2a** with 1.5 equivalents of NaN₃, 3 mol% (relative to **1a**) copper salt, with DMSO ($\eta = 0.50 \,\mu\text{L mg}^{-1}$) at 90 g for 60 minutes. ^d 300 mg of solid with DMSO ($\eta = 0.50 \,\mu\text{L mg}^{-1}$). ^e Coil soaked for 24 h in 2 mL alkyne **2a** in a sealed vial at room temperature. ^f RAM of 300 mg SiO₂, 256 μL **2a**, and DMSO ($\eta = 0.50 \,\mu\text{L mg}^{-1}$) at 90 g for 60 minutes, followed by washing with EtOAc. ^g Reaction performed at a three times larger scale: 6 mmol of **1a** and **2a** each and 9 mmol of NaN₃, with DMSO ($\eta = 0.50 \,\mu\text{L mg}^{-1}$) at 90 g for 60 minutes.

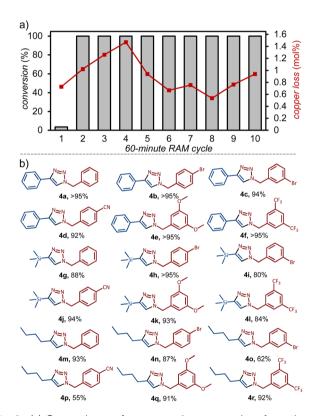


Fig. 2 (a) Conversion to 4a compared to copper loss from the coil (in mol% with respect to 2a) for 10 consecutive 60 minutes RAM cycles conducted using the same copper coil, based on quadruplicate measurements. (b) Substrate scope for herein developed RAM click-coupling reaction, with isolated yields indicated.

obtained by weighing. No correlation was observed between the amount of copper leached and reaction conversion after each reaction cycle – after the first cycle, all reactions exhibited quantitative conversion (Fig. 2a). As using 3 mol% of CuCl as

the catalyst led to only *ca.* 30% conversion to **4a**, we conclude that a significant amount of catalysis must be occurring on the metal coil surface (Table 1, Entries 3–5, also ESI†).²¹

Moreover, we have conducted the catalytic synthesis of 4a using a three-fold increase of starting materials (Table 1, Entry 13). Under these conditions, the amount of copper lost from the coil averaged to 0.95 ± 0.3 mg across four experiments, *i.e.* the amount of copper lost from the coil was now only 0.25 ± 0.08 mol% with respect to the alkyne reactant, while the conversion remained at quantitative level. These observations are consistent with the entire copper coil being exposed to the sample throughout the RAM process, and also support the view that the majority, if not all, of catalysis is taking place on the metal surface and not via copper lost by abrasion.

With reaction conditions for direct mechanocatalysis by RAM in hand, we extended the method to a range of liquid and solid alkyl bromides 1a-1f and alkynes: phenylacetylene (2a), trimethylsilylacetylene (2b), and 1-hexyne (2c). With few exceptions, the expected cycloaddition products 4a-4r (Fig. 2b) were obtained after workup in near-quantitative conversions and >90% isolated yields, following RAM of an equimolar (2 mmol) amount of alkyl bromide and alkyne, with 1.5 equivalents NaN3 in the presence of a copper coil and DMSO liquid additive $(\eta = 0.50 \ \mu L \ mg^{-1})$. The workup consisted of adding 2 mL of ethyl acetate (EtOAc) to the reaction vial, followed by RAM for an additional 5 minutes, and filtration to remove excess NaN3 and the byproduct NaBr. The cycloaddition product was then precipitated by adding 3 mL of a water: MeOH mixture (1:2 v/v), followed by another 5 minutes of RAM and filtration to yield white or yellow solids. For 4g-4l, work-up involved washing with a mixture of concentrated aqueous solution of NH₄Cl and EtOAc (1:2 v/v), before evaporation in vacuo to yield a yellow solid or oil.‡

To verify that the reaction was indeed taking place by RAM rather than during subsequent analysis, the synthesis of 4a was

interrupted after 20 minutes, and immediately accessed by ¹H-NMR in CDCl₃ which revealed *ca.* 25% conversion, and then again 24 hours later, revealing no change in conversion. The products were characterised by ¹H-, ¹³C-NMR, FTIR spectroscopy, and HR-MS, and **4e** was additionally characterized by single crystal X-ray diffraction, confirming that [2 + 3] cycloaddition took place (see ESI†. Investigation of selected samples by scanning electron microscopy (SEM) revealed that crude materials from RAM synthesis were composed of well-developed micrometre-sized crystals (see ESI†).

Noting that the RAM platform should be highly amenable to in situ monitoring,22 we devised a setup for real-time reaction monitoring using Raman spectroscopy, previously not described in the context of RAM mechanochemistry (see ESI†). Specifically, real-time reaction monitoring was done using a RamanRxn1TM analyser by Kaiser Optical Systems Inc., equipped with a power tuneable 1-400 mW 785 nm Raman probe. Spectra were recorded with an integration time of 5–10 seconds and 3–5 accumulations to optimise the signal-to-noise ratio. All spectra were dark and intensity corrected using the Holograms® software package before being processed with MATLAB. In a typical monitoring experiment, a 1-dram volume glass vial was placed in the custommade sample holder containing an entrance slit (Fig. 1b, also ESI†). The 785 nm Raman probe was then placed approximately 10 mm from the vial, with the focus on the vial centre (see ESI†). Using this monitoring setup enabled us to observe linear kinetics for the formation of 4a (Fig. 3a-c).

Accuracy of the method was validated by *ex situ* monitoring of the reaction progress by ¹H NMR in separate experiments, which also showed a linear profile (Fig. 3d). A linear kinetic profile was also observed for the coupling of **2a** with the solid reactant 3,5-dimethoxybenzyl bromide (**1e**) to give the triazole **4e** (see ESI†). Overall, the experimentally observed linear kinetic

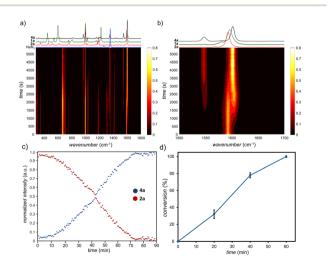


Fig. 3 Time-resolved Raman spectra for *in situ* monitoring of the formation of 4a by RAM direct mechanocatalysis: (a) the entire spectral range and (b) close-up of the 1500–1700 cm⁻¹ range, demonstrating the disappearance of 1a and 2a, and the formation of 4a. (c) Time-resolved changes in intensity of Raman bands corresponding to a decrease of 2a (red) and formation of 4a (blue); (d) *ex situ* reaction profile measured by ¹H-NMR analysis upon dissolution of the entire reaction mixture in CDCl₃.

profiles indicate 0th-order reaction kinetics, consistent with surface catalysis.

Mechanochemical reactions by ball milling have previously been shown to permit excellent control of reaction stoichiometry, enabling selective functionalization of substrates bearing multiple reaction sites.23 In order to investigate if such selectivity is accessible in RAM, we explored the reactivity of the symmetrical dialkyne p-diethynylbenzene (2d) (Fig. 4a). Realtime Raman spectroscopy monitoring revealed that the reaction selectivity is strongly affected by η , even independent of reaction stoichiometry. Specifically, following the reaction of 2d and 1a in a 1:2 respective stoichiometric ratio in the presence of DMSO ($\eta = 0.50 \mu L mg^{-1}$) revealed almost complete conversion into the non-symmetrical 4s within 60 minutes. After 4 hours, only a small amount of the symmetrical 4t was observed. At $\eta = 1.0 \mu L \text{ mg}^{-1}$, however, the reaction rapidly proceeds further and 4s only appears as a reaction intermediate, quantitatively yielding 4t after 2 hours (Fig. 4b and c).14 The ability to selectively obtain either 4s or 4t by RAM contrasts with reactivity observed in solution; performing the same reaction under dilute conditions (10 mol% CuCl, 25 mL DMSO) produced after 24 hours only 4t, in 28% conversion.

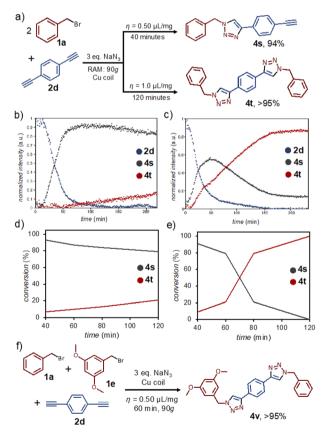


Fig. 4 (a) Reaction of 1a and 2d to form non-symmetrical (4s) and symmetrical (4t) products. In situ Raman data for reactions with: (b) $\eta=0.50~\mu\text{L mg}^{-1}$, and (c) $\eta=1.0~\mu\text{L mg}^{-1}$, showing conversion to 4s (black line) or 4t (red line). NMR monitored conversion accessed over time for reactions with: (d) $\eta=0.50~\mu\text{L mg}^{-1}$, (e) $\eta=1.0~\mu\text{L mg}^{-1}$. (f) Desymmetrization reaction with 1a, 1e and 2d, revealing quantitative conversion to 4v within 60 minutes with DMSO liquid additive ($\eta=0.50~\mu\text{L mg}^{-1}$).

Edge Article Chemical Science

The observations made by in situ Raman monitoring were also confirmed by ¹H NMR analysis of the entire reaction mixture, which revealed selective formation of **4s** at $\eta = 0.50 \ \mu L$ mg⁻¹ within 40 minutes, and switching of the selectivity to 4t at $\eta = 1.0 \ \mu L \ mg^{-1}$ within 2 hours (Fig. 4d, e). The formation of 4s and 4t was verified by 1H- and 13C-NMR, FTIR spectroscopy and HR-MS (see ESI†). The reaction kinetics based on ¹H-NMR analysis of reaction mixtures in separate experiments was similar, but not identical to that based on Raman monitoring, most likely because the latter is limited to only a small fraction of the sample surface. The selectivity for the non-symmetrical 4s at lower η -values might be related to poorer mixing in the presence of NaBr byproduct. This view was supported by two separate experiments. First, the introduction of one equivalent of NaBr to a mixture of 1a and 2a was found to prevent the normally high-yielding formation of 4a within 60 minutes. Second, complete conversion to the di-substituted 4t is readily achieved within 60 minutes of RAM if previously isolated 4s is used as the reactant in combination with one equivalent of 1a.

A similar stepwise process was also observed for the solid reactant **1e**, as established by ¹H-NMR analysis. The reaction of the dialkyne **2d** with **1e** was much faster, however, leading to complete conversion to the disubstituted product **4u** at $\eta=0.50$ μL mg⁻¹ in 60 minutes (see ESI†).

The ability to achieve desymmetrisation of the dialkyne 2d, and the notably higher reactivity observed for 1e compared to 1a under RAM conditions, led us to explore the one-pot synthesis of a non-symmetrical target bis(triazole) 4v (Fig. 4f) directly from equimolar amounts of 1a, 1e, and the dialkyne 2d. After 60 minutes of RAM with a copper coil, 3 equivalents of NaN₃ and DMSO liquid additive ($\eta = 0.50 \ \mu L \ mg^{-1}$), the reaction selectively and quantitatively gave targeted 4v, as confirmed by ¹H- and ¹³C-NMR, ¹H-¹H COSY-NMR, FTIR spectroscopy and HR-MS (see ESI†). The selectivity of this process is remarkable, as the analogous solution reaction using CuCl as catalyst (10 mol%, 25 mL DMSO) gave a mixture of 4s (25%), 4t (18%), **4u** (21%), **4v** (19%), along with the mono-triazole product (16%) arising from a 1:1 reaction of 1a and 1e after 24 hours. Moreover, the high selectivity appears to be associated to using the copper coil as the catalyst, as the RAM reaction using CuCl catalyst (10 mol%) also led to a mixture of products 4s (62%), 4t (2%), **4u** (23%) and **4v** (5%) after 60 minutes. We speculate that selectivity of direct mechanocatalysis for 4v might be related to adsorption of the reactant 2d on the coil surface, and continue to investigate this effect.

Finally, to evaluate the applicability of RAM direct mechanocatalysis for the synthesis of a functional molecule, we targeted Rufinamide, an anti-epileptic triazole-containing API. The RAM reaction of equimolar amounts of 2,5-difluorobenzyl bromide and propiolamide with DMSO ($\eta=0.50~\mu L~mg^{-1}$), 1.5 equivalents of NaN3 and a copper coil, gave Rufinamide in 88% isolated yield after 60 minutes at 90 g, as confirmed by $^1 H$ - and $^{13} C$ -NMR, FTIR spectroscopy and HR-MS (see ESI†). The reaction was readily scalable at least 5-fold, to provide 1.2 grams of Rufinamide within 1 hour. This creates an alternative synthetic route to the high temperatures, long reaction times, and multistep processes currently used in solution. 24

Conclusions

In summary, we have provided the first proof-of-principle for direct mechanocatalysis by resonant acoustic mixing. This work shows that RAM enables using a simple copper coil as the catalyst for rapid, simple, and high-yielding direct-mechanocatalytic copper-catalyzed alkyne-azide coupling on a wide range of substrates, enabling also the simple and gram-scale synthesis of the API Rufinamide. Direct mechanocatalysis by RAM also enabled stoichiometric selectivity greatly superior to that seen when using a more conventional CuCl catalyst, either in solution or under ball-milling conditions, enabling the high-yielding, rapid and one-pot synthesis of non-symmetrical products from an initially symmetrical dialkyne reactant. Herein introduced technique for real-time Raman spectroscopy monitoring, validated by stepwise 1H NMR spectroscopy analysis, reveals that reactions follow a 0th-order kinetic profile consistent with surface catalysis. Overall, this work shows that direct mechanocatalysis can occur in a mild, impact-free environment, relying solely on high-speed mixing of reagents against a copper surface. This offers a basis for the further simplification and development of highly selective mechanochemical surface-catalysed synthesis using the so far poorly explored but readily scalable RAM platform. More broadly, reactions involving raw metals either as catalysts or reactants are emerging as a particularly interesting area of mechanochemistry, and the herein presented work opens an exciting new entry to such developments, based on the RAM technology.25

Data availability

Details of experimental procedures, and selected NMR, FTIR spectroscopy, HR-MS, ICP-MS, SEM, XPS, and single crystal X-ray diffraction data are provided in the ESI.†

Author contributions

All authors have contributed to the writing of this manuscript. Development of mechanochemical synthesis procedure and characterization was performed by CBL and LG, *in situ* Raman spectroscopy monitoring was done by CBL and THB. The research was organized and coordinated by SGK, KN, and TF.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We thank the support of the NSERC Discovery Grant (RGPIN-2017-06467); NSERC John C. Polanyi Award (JCP 562908-2022); Tier-1 Canada Research Chair Program (TF); NSERC CGS-D Scholarship (CBL); Leverhulme International Professorship (TF) and the University of Birmingham. GenenTech, Inc. is acknowledged for support.

Notes and references

‡ Workup was developed to minimise overall solvent consumption, with aqueous MeOH serving to hydrolyze any remaining benzyl bromide or benzyl azide reactant.

- (a) J. Andersen and J. Mack, Green Chem., 2018, 20, 1435–1443; (b) J. L. Howard, Q. Cao and D. L. Browne, Chem. Sci., 2018, 9, 3080–3094; (c) W. Pickhardt, S. Grätz and L. Borchardt, Chem.-Eur. J., 2020, 26, 12903–12911; (d) O. Maurin, P. Verdié, G. Subra, F. Lamaty, J. Martinez and T.-X. Métro, Beilstein J. Org. Chem., 2017, 13, 2087–2093; (e) T. Friščić, C. Mottillo and H. M. Titi, Angew. Chem., Int. Ed., 2020, 59, 1018–1029.
- 2 (a) D. Tan and F. García, Chem. Soc. Rev., 2019, 48, 2274–2292; (b) N. R. Rightmire and T. P. Hanusa, Dalton Trans., 2016, 45, 2352–2362.
- 3 (a) C. Bolm and J. G. Hernández, *Angew. Chem., Int. Ed.*, 2019,
 58, 3285-3299; (b) P. A. Julien, C. Mottillo and T. Friščić, *Green Chem.*, 2017, 19, 2729-2747.
- 4 (a) P. Baláž, M. Achamovičová, M. Baláž, P. Billik, Z. Cherkezova-Zheleva, J. M. Criado, F. Delogu, E. Dutková, E. Gaffet, F. J. Gotor, R. Kumar, I. Mitov, T. Rojac, M. Senna, A. Streletskii and K. Wieczorek-Ciurowa, *Chem. Soc. Rev.*, 2013, 42, 7571–7637; (b) A. A. L. Michalchuk, E. V. Boldyreva, A. M. Belenguer, F. Emmerling and V. V. Boldyrev, *Front. Chem.*, 2021, 9, 685789.
- (a) S. L. James, C. J. Adams, C. Bolm, D. Braga, P. Collier, T. Friščić, F. Grepioni, K. D. M. Harris, G. Hyett, W. Jones, A. Krebs, J. Mack, L. Maini, A. G. Orpen, I. P. Parkin, W. C. Shearouse, J. W. Steed and D. C. Waddell, *Chem. Soc. Rev.*, 2012, 41, 413–447; (b) E. Boldyreva, *Chem. Soc. Rev.*, 2013, 42, 7719–7738; (c) A. Bose and P. Mal, *Beilstein J. Org. Chem.*, 2019, 15, 881–900; (d) R. T. O'Neill and R. Boulatov, *Nat. Rev. Chem.*, 2021, 5, 148–167; (e) D. E. Crawford, C. K. G. Miskimmin, A. B. Albadarin, G. Walker and S. L. James, *Green Chem.*, 2017, 19, 1507–1518.
- 6 (a) D. Tan, L. Loots and T. Friščić, *Chem. Commun.*, 2016, 52, 7760–7781; (b) E. Colacino, A. Porcheddu, C. Charnay and F. Delogu, *React. Chem. Eng.*, 2019, 4, 1179.
- 7 (a) J. G. Hernández and C. Bolm, J. Org. Chem., 2017, 82, 4007–4019; (b) K. Kubota, R. Takahashi and H. Ito, Chem. Sci., 2019, 10, 5837–5842.
- 8 (a) R. F. Koby, T. P. Hanusa and N. D. Schley, *J. Am. Chem. Soc.*, 2018, **140**, 15934–15942; (b) R. A. Haley, A. R. Zellner, J. A. Krause, H. Guan and J. Mack, *ACS Sustainable Chem. Eng.*, 2016, **4**, 2464–2469; (c) F. Cuccu, L. DeLuca, F. Delogu, E. Colacino, N. Solin, R. Mocci and A. Porcheddu, *ChemSusChem*, 2022, **15**, e202200362.
- 9 (a) J. G. Osorio, E. Hernández, R. J. Romañach and F. J. Muzzio, *Powder Technol.*, 2016, 297, 349–356; (b) A. Vandenberg and K. Wille, *Constr. Build. Mater.*, 2018, 164, 716–730; (c) D. H. Leung, D. J. Lamberto, L. Liu, E. Kwong, T. Nelson, T. Rhodes and A. Bak, *Int. J. Pharm.*, 2014, 473, 10–19.
- 10 (a) C. J. Wright, P. J. Wilkinson, S. E. Gaulter, D. Fossey, A. O. Burn and P. P. Gill, *Propellants, Explos., Pyrotech.*,

- 2021, **46**, 1–15; (*b*) M. Solares-Briones, G. Coyote-Dotor, J. C. Páez-Franco, M. R. Zermeño-Ortega, C. M. de le O Contreras, D. Canseco-González, A. Avila-Sorrosa, D. Morales-Morales and J. M. Germán-Acacio, *Pharmaceutics*, 2021, **13**, 790.
- 11 (a) L. Gonnet, C. B. Lennox, J.-L. Do, I. Malvestiti, S. G. Koenig, K. Nagapudi and T. Friščić, Angew. Chem., Int. Ed., 2022, 61, e202115030; (b) L. Gonnet, T. H. Borchers, C. B. Lennox, J. Vainauskas, Y. Teoh, H. M. Titi, C. J. Barrett, S. G. Koenig, K. Nagapudi and T. Friščić, Faraday Discuss., 2023, 241, 128–149; (c) H. M. Titi, J.-L. Do, A. J. Howarth, K. Nagapudi and T. Friščić, Chem. Sci., 2020, 11, 7578–7584; (d) K. Nagapudi, E. Y. Umanzor and C. Masui, Int. J. Pharm., 2017, 521, 337–345; (e) F. Effaty, L. Gonnet, S. G. Koenig, K. Nagapudi, X. Ottenwaelder and T. Friščić, Chem. Commun., 2023, 59, 1010–1013.
- 12 A similar induction period was seen for direct mechanocatalysis by ball-milling:(a) W. Su, J. Yu, Z. Li and Z. Jiang, *J. Org. Chem.*, 2011, 76, 9144–9150; (b) L. Chen, D. Leslie, M. G. Coleman and J. Mack, *Chem. Sci.*, 2018, 9, 4650–4661; (c) T. L. Cook, J. A. Walker and J. Mack, *Green Chem.*, 2013, 15, 617; (d) C. G. Vogt, S. Grätz, S. Lukin, I. Halasz, M. Etter, J. D. Evans and L. Borchardt, *Angew. Chem., Int. Ed.*, 2019, 58, 18942–18947.
- 13 Y. Zhao, S. V. Rocha and T. M. Swager, *J. Am. Chem. Soc.*, 2016, **138**, 13834–13837.
- 14 Appearance of a mono-substituted intermediate in the mechanochemical click reaction of a di-alkyne was previously observed for the ball-milling reaction of 2d with decyl azide, see: R. Thorwirth, A. Stolle, B. Ondruschka, A. Wild and U. S. Schubert, *Chem. Commun.*, 2011, 47, 4370-4372.
- (a) D. A. Fulmer, W. C. Shearouse, S. T. Medonza and J. Mack, *Green Chem.*, 2009, 11, 1821–1825; (b) S. Hwang, S. Grätz and L. Borchardt, *Chem. Commun.*, 2022, 58, 1661–1671; (c) R. A. Haley, J. Mack and H. Guan, *Inorg. Chem. Front.*, 2017, 4, 52–55; (d) M. Wolgemuth, M. Mayer, M. Rappen, F. Schmidt, R. Saure, S. Grätz and L. Borchardt, *Angew. Chem., Int. Ed.*, 2022, 61, e202212694.
- 16 S. Jung and H. J. Yoon, *Angew. Chem., Int. Ed.*, 2021, **59**, 4883–4887.
- 17 (a) W. Pickhardt, S. Grätz and L. Borchardt, Chem.-Eur. J.,
 2020, 26, 12903-12911; (b) L. Chen, M. O. Bovee,
 B. E. Lemma, K. S. M. Keithley, S. L. Pilson,
 M. G. Coleman and J. Mack, Angew. Chem., Int. Ed., 2015,
 54, 11084-11087.
- 18 (a) W. Su, J. Yu, Z. Li and Z. Jiang, J. Org. Chem., 2011, 76, 9144–9150; (b) C. G. Vogt, S. Grätz, S. Lukin, I. Halasz, M. Etter, J. D. Evans and L. Borchardt, Angew. Chem., Int. Ed., 2019, 58, 18942–18947.
- (a) Y. Sawama, N. Yasukawa, K. Ban, R. Goto, M. Niikawa,
 Y. Monguchi, M. Itoh and H. Sakiji, *Org. Lett.*, 2018, 20,
 2892–2896; (b) Y. Sawama, M. Niikawa and H. Sajiki, *J. Synth. Org. Chem.*, *Jpn.*, 2019, 77, 1070–1077.
- 20 C. G. Vogt, M. Oltermann, W. Pickhardt and S. Grätz, *Adv. Energy Sustainability Res.*, 2021, **2**, 2100011.

Edge Article Chemical Science

- 21 The Borchardt group has recently shown that catalysis in the Suzuki-Miyaura reactions conducted using a palladium-based milling assembly occurs exclusively on the ball, rather than abraded material, see: W. Pickhardt, C. Beaković, M. Mayer, M. Wohlgemuth, F. J. L. Kraus, M. Etter, S. Grätz and L. Borchardte, *Angew. Chem., Int. Ed.*, 2022, **61**, e202205003.
- 22 (a) A. A. L. Michalchuk, K. S. Hope, S. R. Kennedy, M. V. Blanco, E. V. Boldyreva and C. R. Pulham, *Chem. Commun.*, 2018, 54, 4033–4036; (b) A. G. Buzanich, C. T. Cakir, M. Radtke, M. B. Haider, F. Emmerling, P. F. M. de Oliveira and A. A. L. Michalchuk, *J. Chem. Phys.*, 2022, 157, 214202; (c) G. I. Lampronti, A. A. L. Michalchuk, P. P. Mazzeo, A. M. Belenguer, J. K. M. Sanders, A. Bacchi and F. Emmerling, *Nat. Commun.*, 2021, 12, 6134.
- 23 (a) V. Štrukil, D. Margetić, M. D. Igrc, M. Eckert-Maksić and T. Friščić, *Chem. Commun.*, 2012, 48, 9705–9707; (b) M. Ferguson, N. Giri, X. Huang, D. Apperley and S. L. James, *Green Chem.*, 2014, 16, 1374–1382; (c) J. L. Howard, Y. Sagatov, L. Repusseau, C. Schotten and D. L. Browne, *Green Chem.*, 2017, 19, 2798–2802; (d) T. Seo, K. Kubota and H. Ito, *J. Am. Chem. Soc.*, 2020, 142, 9884–

- 9889; (e) R. Schmidt, A. Stolle and B. Ondruschka, *Green Chem.*, 2012, 14, 1673.
- 24 (a) R. Portmann and A. G. Novartis, Basel, Switzerland. U.S. Patent 6,156,907, 2000; (b) P. Bodhuri, S. P. Green, A. Karadeolian, and E. G. Cammisa, Apotex Technologies Inc., WO2014121383A1, 2014.
- 25 For recent ball-milling examples, see: (a) A. C. Jones, M. T. J. Williams, L. C. Morrill and D. L. Browne, ACS Catal., 2022, 12, 13681-13689; (b) Q. Cao, J. L. Howard, E. Wheatley and D. L. Browne, Angew. Chem., Int. Ed., 2018, 130, 11509-11513; (c) R. R. A. Bolt, L. C. Morrill, E. Richards and D. L. Browne, Angew. Chem., Int. Ed., 2021, 60, 23128-23133; (d) W. I. Nicholson, J. L. Howard, G. Magri, A. C. Serastram, A. Khan, R. R. A. Bolt, L. C. Morrill, E. Richards and D. L. Browne, Angew. Chem., Int. Ed., 2021, 60, 23128-23133; (e) P. Gao, J. Jiang, S. Maeda, K. Kubota and H. Ito, Angew. Chem., Int. Ed., 2022, 41, e202207118; (f) R. Takahashi, A. Hu, P. Gao, Y. Pang, T. Seo, J. Jiang, S. Maeda, H. Takaya, K. Kubota and H. Ito, Nat. Commun., 2021, 12, 6691; (g) V. S. Pfennig, R. C. Viellella, J. Nikodemus and C. Bolm, Angew. Chem., Int. Ed., 2022, 61, e202116514; (h) I. R. Speight and T. P. Hanusa, Molecules, 2020, 25, 570.