

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Sustainable Energy Fuels*,  
2024, 8, 1260Z-scheme water splitting utilizing  $\text{CuLi}_{1/3}\text{Ti}_{2/3}\text{O}_2$  as  
a hydrogen-evolving photocatalyst with photo-  
response up to 600 nm<sup>†</sup>Shunya Yoshino,<sup>a</sup> Tanya Kurutach,<sup>ab</sup> Qingshan Liu,<sup>ab</sup> Toshiaki Yamanaka,<sup>ab</sup>  
Shunsuke Nozawa,<sup>c</sup> Makoto Kobayashi,<sup>ib d</sup> Hiromu Kumagai<sup>ib e</sup>  
and Hideki Kato<sup>ib \*a</sup>

$\text{CuLi}_{1/3}\text{Ti}_{2/3}\text{O}_2$  (CLTO) is a visible-responsive photocatalyst, whose photo-response reaches up to 600 nm, for  $\text{H}_2$  evolution using sacrificial electron donors such as methanol and  $\text{S}^{2-}$ . In this study, utilization of CLTO in Z-scheme water splitting (Z-WS) was investigated. The photocatalytic performance of  $\text{Cr}_2\text{O}_3/\text{M}/\text{CLTO}$  as a  $\text{H}_2$ -evolving photocatalyst, which was prepared by sequential photodeposition of cocatalysts (M: Ru, Rh, Pd and Pt) and  $\text{Cr}_2\text{O}_3$ , was evaluated for Z-WS using  $\text{BiVO}_4$ , an  $\text{O}_2$ -evolving photocatalyst, and a  $\text{Co}(\text{bpy})_3^{3+/2+}$  redox shuttle under visible light. Among the examined samples,  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO}$  produced both  $\text{H}_2$  and  $\text{O}_2$  with meaningful rates. Thus, CLTO was first utilized in a visible responsive Z-scheme system for water splitting. The  $\text{Cr}_2\text{O}_3$  layer played a significant role in the suppression of backward reactions, such as reduction of  $\text{Co}(\text{bpy})_3^{3+}$ . The activity of  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO}$  for Z-WS was remarkably affected by the deposition conditions of the Ru cocatalyst. The activity for Z-WS was remarkably improved when the photodeposition of the Ru cocatalyst was conducted in a methanol solution of  $\text{RuCl}_3$ . Unusually large plate Ru species with 100–200 nm sizes and about 30 nm thickness were present in the highly active sample. Characterization using X-ray photoelectron spectroscopy and X-ray absorption spectroscopy indicated that the Ru cocatalyst was deposited as mainly the oxyhydroxide of Ru. Z-WS also proceeded in the absence of  $\text{Co}(\text{bpy})_3^{3+/2+}$  (the system based on interparticle electron transfer), however, the Z-scheme system using the  $\text{Co}(\text{bpy})_3^{3+/2+}$  electron shuttle showed 10 times higher activity than the interparticle electron transfer system. The external quantum yield and efficiency of solar energy conversion to hydrogen were determined to be 0.5% at 430 nm and 0.029%, respectively.

Received 13th December 2023  
Accepted 5th February 2024

DOI: 10.1039/d3se01622f

[rsc.li/sustainable-energy](https://rsc.li/sustainable-energy)

## Introduction

Solar water splitting is a promising reaction to convert solar energy, the most abundant renewable energy, to  $\text{H}_2$ , a storable chemical fuel.<sup>1–3</sup> Photocatalytic water splitting has been demonstrated to show high quantum yields exceeding 50% using ultraviolet (UV) responsive photocatalysts such as  $\text{NaTaO}_3\text{:La}$ ,  $\text{Ga}_2\text{O}_3\text{:Zn}$  and  $\text{SrTiO}_3\text{:Al}$ .<sup>4–6</sup> However, they are not eligible for practical use because their wide band gaps restrict

the usable wavelength in the solar spectrum to very narrow ranges. Construction of photocatalytic Z-scheme systems is a beneficial approach to water splitting under visible light because Z-scheme water splitting (Z-WS) can be achieved by combining two kinds of photocatalysts incapable of water splitting when used alone.<sup>7–9</sup> Thus, many Z-scheme systems have been reported for photocatalytic water splitting under visible light.<sup>7–18</sup>  $\text{SrTiO}_3\text{:Rh}$  and  $\text{BiVO}_4$ , which have been developed for sacrificial  $\text{H}_2$  and  $\text{O}_2$  evolution under visible light,<sup>19,20</sup> are frequently used in Z-scheme systems as a  $\text{H}_2$ -evolving photocatalyst (HEP) and an  $\text{O}_2$ -evolving photocatalyst (OEP), respectively. The  $\text{SrTiO}_3\text{:Rh}-\text{BiVO}_4$  pair is one of the representative ones in the Z-scheme system and is available to systems with various routes of electron transfer from the OEP to HEP: redox electron mediators ( $\text{Fe}^{3+/2+}$ ,  $\text{Co}(\text{bpy})_3^{3+/2+}$  and  $\text{IO}_3^-/\text{I}^-$ ), solid state electron mediators (reduced graphene oxide (RGO), carbon and metallic layer) and without any electron mediators (direct interparticle electron transfer).<sup>10,15,18,21–25</sup> In particular, a photocatalyst sheet composed of  $\text{SrTiO}_3\text{:Rh}$ ,  $\text{BiVO}_4$  and a Au layer showed high performance in water splitting exceeding 1% efficiency of solar energy conversion to hydrogen (STH) and

<sup>a</sup>Institute of Multidisciplinary Research for Advanced Materials, Tohoku University, Sendai 980-8577, Japan. E-mail: [hideki.kato.e2@tohoku.ac.jp](mailto:hideki.kato.e2@tohoku.ac.jp)<sup>b</sup>Department of Applied Chemistry, Graduate School of Engineering, Tohoku University, Sendai 980-8579, Japan<sup>c</sup>Institute of Materials Structure Science, High Energy Accelerator Research Organization, Tsukuba 305-0801, Japan<sup>d</sup>Institute of Materials and Systems for Sustainability, Nagoya University, Nagoya 464-8601, Japan<sup>e</sup>Research Center for Advanced Science and Technology, The University of Tokyo, Tokyo 153-8904, Japan<sup>†</sup> Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3se01622f>

30% external quantum yield (EQY) at 420 nm.<sup>25</sup> This demonstrates the promising potential of the Z-scheme system for water splitting. However, use of photocatalysts with response to longer wavelengths is desired, because the absorption edges of SrTiO<sub>3</sub>:Rh and BiVO<sub>4</sub>, which lie at 540 and 520 nm respectively, are insufficient for utilization of sunlight.<sup>26</sup>

Utilization of photocatalysts with response to longer wavelengths compared with SrTiO<sub>3</sub>:Rh and BiVO<sub>4</sub> has been extensively studied. It has enlarged the library of long-wavelength responsive photocatalysts available for Z-scheme systems, for example, metal oxides such as CuLi<sub>1/3</sub>Ti<sub>2/3</sub>O<sub>2</sub> (CLTO), ZnRh<sub>2</sub>O<sub>4</sub>, NaTaO<sub>3</sub>:Ir and BaTa<sub>2</sub>O<sub>6</sub>:Ir, (oxy)nitrides such as BaTaO<sub>2</sub>N, Ta<sub>3</sub>N<sub>5</sub> and LaMg<sub>1/3</sub>Ta<sub>2/3</sub>O<sub>2</sub>N and (oxy)sulfides such as Sm<sub>2</sub>Ti<sub>2</sub>-O<sub>5</sub>S<sub>2</sub>, Ga-La<sub>5</sub>Ti<sub>2</sub>CuO<sub>7</sub>S<sub>5</sub> and CuGa<sub>0.8</sub>In<sub>0.2</sub>S<sub>2</sub> as HEPs, as well as metal oxides such as Bi<sub>4</sub>V<sub>2</sub>O<sub>11</sub>, SrTiO<sub>3</sub>:Ir and KNbO<sub>3</sub>:Ir,Sb, (oxy) nitrides such as Ta<sub>3</sub>N<sub>5</sub>, LaTiO<sub>2</sub>N and La<sub>0.5</sub>Sr<sub>0.5</sub>Ta<sub>0.5</sub>Ti<sub>0.5</sub>O<sub>2</sub>N, oxychlorides such as Bi<sub>4</sub>NbO<sub>8</sub>Cl and natural photosystem II as OEPs.<sup>27–41</sup> To improve the properties of Z-scheme systems, expanding the combination of HEPs and OEPs as well as enhancing the performance of photocatalysts is important. Among the aforementioned photocatalysts, CLTO is an attractive HEP for the topic of expanding combination in the Z-scheme system. CLTO, which is a delafossite-type Cu(I)-titanate discovered in 2015,<sup>42</sup> produces H<sub>2</sub> in the presence of sacrificial reagents such as methanol and a mixture of S<sup>2–</sup> and SO<sub>3</sub><sup>2–</sup> with photo-response up to 600 nm. Kudo *et al.* have achieved Z-WS employing Pt-deposited CLTO and RGO-modified TiO<sub>2</sub>,<sup>31</sup> however excitation by UV light is indispensable for this system to excite the TiO<sub>2</sub> component. Other Z-scheme systems utilizing CLTO have not been reported so far, thus CLTO has not been combined with visible-responsive OEPs nor redox electron shuttles. Utilization of TiO<sub>2</sub> instead of the common visible responsive OEPs such as BiVO<sub>4</sub> and WO<sub>3</sub> in the previous report implies difficulties in the realization of Z-WS employing RGO-modified BiVO<sub>4</sub> and WO<sub>3</sub> with CLTO. Therefore, Z-scheme systems based on redox electron shuttles sound better than those with RGO-modified OEPs to achieve Z-WS by combining CLTO with a visible responsive OEP.

Use of redox electron shuttles in Z-WS, such as IO<sub>3</sub><sup>–</sup>/I<sup>–</sup>, Fe<sup>3+/2+</sup> and Co(bpy)<sub>3</sub><sup>3+/2+</sup>, often brings unfavourable backward reactions involving the redox couple; that is, reduction of the oxidant occurs on the HEP and oxidation of the reductant occurs on the OEP.<sup>17,43–45</sup> It has been reported that adsorption of redox species on a Pt cocatalyst effectively suppresses the backward reactions on Pt in Z-WS using IO<sub>3</sub><sup>–</sup>/I<sup>–</sup> and Fe<sup>3+/2+</sup>.<sup>17,43,44</sup> Li *et al.* have reported that a photodeposited Cr<sub>2</sub>O<sub>3</sub> layer also hinders reduction of IO<sub>3</sub><sup>–</sup> on the Pt cocatalyst.<sup>45</sup> The universal effects of the Cr<sub>2</sub>O<sub>3</sub> modification are expected in Z-WS using other redox shuttles except under acidic conditions, for which it is necessary to use Fe<sup>3+/2+</sup> and VO<sub>2</sub><sup>+/2+</sup>.

Based on the aforementioned background, we are attracted to Z-WS employing CLTO, visible responsive OEPs and redox shuttles. In particular, BiVO<sub>4</sub>, which functions as an OEP in various kinds of Z-scheme systems, is a good candidate for the OEP. A redox couple of Co(bpy)<sub>3</sub><sup>3+/2+</sup>, which works well with BiVO<sub>4</sub> around neutral pH, is a strong candidate for the redox shuttle in this study. In this work, we examined Z-WS utilizing

CLTO, BiVO<sub>4</sub> and Co(bpy)<sub>3</sub><sup>3+/2+</sup>, and especially the influences of cocatalysts and Cr<sub>2</sub>O<sub>3</sub> modification upon the performance of Z-WS were investigated.

## Experimental

### Preparation of photocatalysts

Powders of CLTO were synthesized by a reaction between Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> and Cu<sub>2</sub>O with the help of a CuCl flux referring to the literature.<sup>42</sup> Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> was prepared by a polymerizable complex (PC) method from Li<sub>2</sub>CO<sub>3</sub> (Wako Pure Chemical, 99.0%) and titanium tetrabutoxide (Kanto Chemical, 97.0%) as raw materials using citric acid (Wako Pure Chemical, 98%) and propylene glycol (Kanto Chemical, 99.0%) as chelating and esterification reagents. The obtained precursor was heated at 800 °C for 5 h in air to obtain a crystalline Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> powder. The Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> powder was subjected to milling treatment using a pot mill rotator (As One, PM-001S). Briefly, 1.5 g of Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> was put in a 250 mL plastic bottle with 30 mL of distilled water and 60 g of stabilized zirconia balls (φ10 mm), then the bottle was rotated at 250 rpm for 20 h. This milling treatment was effective to reduce the size of secondary particles of Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> obtained by the PC method as shown in Fig. S1.† Synthesis of CLTO from milled Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> and Cu<sub>2</sub>O was performed at 600 and 700 °C for 10 h in a vacuumed silica tube. After the heat treatment, the remaining Cu<sub>2</sub>O and CuCl were washed with 2 M NH<sub>3</sub> solution. BiVO<sub>4</sub> was prepared from Bi<sub>2</sub>O<sub>3</sub> (Wako Pure Chemical, 99.9%) and V<sub>2</sub>O<sub>5</sub> (Kanto Chemical, 99.0%) by a liquid solid reaction method in 0.8 M HNO<sub>3</sub> at 80 °C according to the literature.<sup>46</sup> SrTiO<sub>3</sub>:Rh used as a reference photocatalyst was prepared by a spray drying method as previously reported.<sup>47</sup>

For a cocatalyst survey, M (0.05 wt%)/CLTO (M: Ru, Rh, Pd and Pt) was prepared by a photodeposition method in an aqueous 10 vol% methanol solution using RuCl<sub>3</sub>·*n*H<sub>2</sub>O (Wako Pure Chemical, 99.9%), Rh(NO<sub>3</sub>)<sub>3</sub> (Wako Pure Chemical, 95%), PdCl<sub>2</sub> (Wako Pure Chemical, 99.0%) and H<sub>2</sub>PtCl<sub>6</sub>·6H<sub>2</sub>O (Kanto Chemical, 99.0%) as precursors. CLTO (0.3 g) was dispersed in a 10 vol% methanol solution containing the cocatalyst source, whose pH was adjusted to 10 by adding an aqueous NaOH solution. The suspension was irradiated with visible light (λ >420 nm) using a 300 W Xe-arc lamp (Excelitas, Cermex PE300BF) with a long pass filter. Cr<sub>2</sub>O<sub>3</sub> modification for M/CLTO (0.2 g) was also performed by a photodeposition method using K<sub>2</sub>CrO<sub>4</sub> (Kanto Chemical, 99.0%) in a 10 vol% methanol solution,<sup>48</sup> where the concentration of K<sub>2</sub>CrO<sub>4</sub> was 0.02 mM corresponding to 1.2 wt% of Cr<sub>2</sub>O<sub>3</sub> if the whole chromium was deposited. For the Ru cocatalyst, the deposition conditions including an impregnation method were investigated in more detail. For photodeposition of the Ru cocatalyst, two kinds of reactant solutions, 100% methanol and an aqueous solution containing 0.1 M Na<sub>2</sub>S and 0.5 M Na<sub>2</sub>SO<sub>3</sub>, were examined in addition to the 10 vol% methanol solution. These samples were denoted as Ru(10% MeOH), Ru(100% MeOH) and Ru(S<sup>2–</sup>). In the impregnation method, CLTO was put in an aqueous RuCl<sub>3</sub> solution, then water was evaporated by heating. The dried powder was subjected to heat treatment at 200 °C in N<sub>2</sub>, 200 °C under vacuum and 150 °C in H<sub>2</sub>, the samples thus obtained



were denoted as Ru(N<sub>2</sub>), Ru(evac) and Ru(H<sub>2</sub>), respectively. It should be noted that treatment in air was not conducted because of easy oxidation of Cu<sup>+</sup> in CLTO.

### Characterization of photocatalysts

The crystal phases of the samples were analyzed by X-ray diffraction using Cu K $\alpha$  radiation (XRD; Bruker AXS, D2 phaser). The samples were observed using scanning electron microscopes (SEM; Hitachi, SU1510 and S-4800) and a transmission electron microscope (TEM; Jeol, JEM-2100F/HK) with 200 kV acceleration voltage. The diffuse reflectance spectra of the samples were obtained using an ultraviolet-visible-near infrared spectrometer (Jasco, V-770) equipped with an integrating sphere and were converted by the Kubelka–Munk method. The specific surface areas ( $S_{\text{BET}}$ ) of the samples were determined by N<sub>2</sub> adsorption at 77 K and BET analysis (MicrotracBEL, BELSORP-miniII). X-ray photoelectron spectra (XPS) were obtained using Kratos apparatus (ESCA-3400) with Mg K $\alpha$  radiation as the excitation source. Measurements of X-ray absorption fine structure (XANES and EXAFS) at the Ru K-edge were carried out in a fluorescence mode at the NW10A beamline of the Photon Factory Advanced Ring in the High Energy Accelerator Research Organization (Tsukuba, Japan). The incident X-ray was monochromatized by a Si(311) double-crystal monochromator.

### Photocatalytic reactions

Sacrificial H<sub>2</sub> evolution and Z-WS were conducted using a top-window reaction vessel connected to a gas-closed circulation system. Appropriate amounts of samples were dispersed in 160 mL of a reactant solution. Solutions of a 10 vol% methanol, 0.1 M Na<sub>2</sub>S and 0.5 M Na<sub>2</sub>SO<sub>3</sub> mixture and 0.5 mM Co(bpy)<sub>3</sub>SO<sub>4</sub> were used for H<sub>2</sub> evolution. For Z-WS, CLTO (50 mg) and BiVO<sub>4</sub> (50 mg) were dispersed in a 0.1 mM Co(bpy)<sub>3</sub>SO<sub>4</sub> solution. For general experiments, 10 kPa of Ar was introduced into the system after deaeration. The suspension was irradiated with visible light ( $\lambda > 420$  nm) using a 300 W Xe-arc lamp with a long pass filter. In addition, monochromatic lights at 430 and 560 nm emitted from light-emitting diodes (LED; Asahi Spectra, CL-H1-430-9-1-B and CL-H1-568-9-1-B) attached with band pass filters (Asahi Spectra, HMX0430 and MX0560), whose power was 68.5 mW for 430 nm and 11.2 mW for 560 nm, were also used to evaluate EQY and photo-response. To evaluate the efficiency of solar energy conversion to hydrogen (STH), a solar simulator with 100 mW cm<sup>-2</sup> incident density and 16 cm<sup>2</sup> irradiation area (Asahi spectra, HAL-320) was also used. The evolved gas was analyzed using an online gas chromatograph (Shimadzu, GC-8A with MS-5A column, TCD detector and Ar carrier).

### Electrochemical measurements

Cyclic voltammogram (CV) measurements were performed using bare and Cr<sub>2</sub>O<sub>3</sub>-coated fluorine-doped tin oxide (FTO) electrodes. Cr<sub>2</sub>O<sub>3</sub>/FTO was prepared by electrical reduction of K<sub>2</sub>CrO<sub>4</sub> at -0.2 V vs. RHE for 3 min in 0.1 M K<sub>2</sub>SO<sub>4</sub> containing 0.1 mM K<sub>2</sub>CrO<sub>4</sub>. Measurements were performed in an aqueous solution containing 0.1 M K<sub>2</sub>SO<sub>4</sub> and 0.1 mM Co(bpy)<sub>3</sub>SO<sub>4</sub> under an Ar atmosphere. A platinum wire and Ag/AgCl in

saturated KCl were used as counter and reference electrodes, respectively. Electric potential was swept at a rate of 20 mV s<sup>-1</sup>.

## Results and discussion

### Synthesis of CLTO

There are two polymorphs of CLTO belonging to trigonal and hexagonal systems which are regarded as low- and high-temperature phases, respectively. The CLTO sample prepared at 600 °C was a mixture of trigonal and hexagonal phases whereas that at 700 °C was obtained as a hexagonal phase as reported previously (Fig. S2a†).<sup>42</sup> Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub>, the precursor used in the synthesis of CLTO, remained in both samples. Both samples showed the same absorption onset at 600 nm wavelength, being consistent with previous reports (Fig. S2b†).<sup>31,42</sup> As shown in Fig. S3,† the particle sizes of the CLTO samples synthesized at 600 and 700 °C were 2–5 and 3–10  $\mu\text{m}$ , respectively, thus higher synthesis temperature remarkably promoted crystal growth. Accordingly,  $S_{\text{BET}}$  of CLTO decreased from 0.6 to 0.2 m<sup>2</sup> g<sup>-1</sup> upon increasing the synthesis temperature from 600 to 700 °C. The photocatalytic performance of the CLTO samples was evaluated for sacrificial H<sub>2</sub> evolution from an aqueous solution containing 0.1 M Na<sub>2</sub>S and 0.5 M Na<sub>2</sub>SO<sub>3</sub> with an *in situ* photodeposited Ru cocatalyst (Fig. S4†). Both samples produced H<sub>2</sub> by visible light excitation, and the 600 °C sample containing tri-CLTO as the majority phase exhibited higher activity than the 700 °C sample containing hex-CLTO with a trace of Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub>. The Li<sub>4</sub>Ti<sub>5</sub>O<sub>12</sub> phase, which remained in both samples, gave no photocatalytic activity under visible light because of its wide band gap (3.7 eV), indicating that CLTO phases were responsible for the activity under visible light. Kudo *et al.* reported that both trigonal and hexagonal phases were active and the activity of the hexagonal phase (143  $\mu\text{mol h}^{-1}$ ) was higher than that of the trigonal one (103  $\mu\text{mol h}^{-1}$ ).<sup>31</sup> Interestingly, our CLTO showed the opposite tendency where the activity of the tri-CLTO rich sample (402  $\mu\text{mol h}^{-1}$ ) was much higher than that of the hex-CLTO rich sample (117  $\mu\text{mol h}^{-1}$ ). This indicates that not only crystal phases but also other properties such as defects and particle size, which are influenced by synthetic conditions, strongly affect the photocatalytic performance of CLTO. The EQY of the 600 °C sample for this sacrificial H<sub>2</sub> evolution was determined to be 2.5% and 2.2% at 430 and 560 nm, respectively. Thus, the successful synthesis of CLTO exhibiting moderate photocatalytic activity at long wavelength was confirmed. The 600 °C sample was used for further experiments.

### Cocatalyst survey for Z-WS

Surveying effective cocatalysts was conducted for construction of Z-scheme systems utilizing CLTO as an HEP. Fig. 1a shows H<sub>2</sub> evolution from a 10 vol% methanol solution over *in situ* photodeposited M/CLTO. It should be noted that the Ru/CLTO sample in this section corresponded to Ru(10% MeOH)/CLTO in the following sections. The bare CLTO was not active for H<sub>2</sub> evolution, therefore cocatalyst modification was indispensable for H<sub>2</sub> evolution by CLTO. The highest activity was obtained



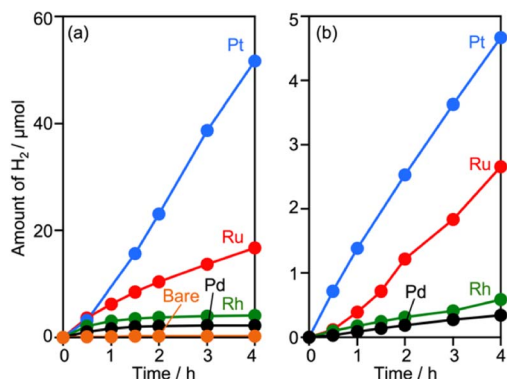


Fig. 1 Sacrificial  $\text{H}_2$  evolution from a 10% methanol solution over (a) M (0.05 wt%)/CLTO and (b)  $\text{Cr}_2\text{O}_3$ (1.2 wt%)/M(0.05 wt%)/CLTO. Photocatalyst: 0.3 g for (a) and 0.2 g for (b); reactant solution: 10% methanol solution, 160 mL; light source: 300 W Xe lamp ( $\lambda > 420$  nm).

with a Pt cocatalyst. A Ru cocatalyst also exhibited relatively high activity while Rh and Pd cocatalysts were less effective.  $\text{H}_2$  evolution rates were remarkably decreased upon deposition of  $\text{Cr}_2\text{O}_3$  irrespective of the kinds of cocatalysts (Fig. 1b). The order of effectiveness of cocatalysts in sacrificial  $\text{H}_2$  evolution using methanol was not changed by deposition of  $\text{Cr}_2\text{O}_3$ . The  $\text{Cr}_2\text{O}_3$ /M/CLTO samples were examined for Z-WS combined with  $\text{BiVO}_4$  and  $\text{Co}(\text{bpy})_3\text{SO}_4$ . Both  $\text{H}_2$  and  $\text{O}_2$  were evolved in all cases as shown in Fig. 2. This fact indicates that cocatalyst-modified CLTO functions as an HEP using  $\text{Co}(\text{bpy})_3^{2+}$  because  $\text{BiVO}_4$  is incapable of  $\text{H}_2$  evolution. The reactions started with  $\text{Co}(\text{bpy})_3^{2+}$ , which worked as an electron donor, therefore the occurrence of  $\text{O}_2$  evolution proved the achievement of the Z-scheme mechanism between CLTO and  $\text{BiVO}_4$ .<sup>23,39</sup>  $\text{BiVO}_4$  oxidized water accompanied with the reduction of  $\text{Co}(\text{bpy})_3^{3+}$  which was the representative of holes generated in CLTO. Among those examined,  $\text{Cr}_2\text{O}_3$ /Pt and  $\text{Cr}_2\text{O}_3$ /Ru exhibited similar activity in the early stage of reaction although  $\text{Cr}_2\text{O}_3$ /Pt showed higher activity than  $\text{Cr}_2\text{O}_3$ /Ru in sacrificial  $\text{H}_2$  evolution using methanol. The lower activity of  $\text{Cr}_2\text{O}_3$ /Pt in Z-WS would be due to water formation from  $\text{H}_2$  and  $\text{O}_2$ . Water formation in the

dark was examined for Ru/CLTO and  $\text{Cr}_2\text{O}_3$ /M/CLTO (M: Rh, Pd and Pt) to see the effects of  $\text{Cr}_2\text{O}_3$  deposition (Fig. S5†). Only  $\text{Cr}_2\text{O}_3$ /Pt/CLTO showed the decrease of  $\text{H}_2$  and  $\text{O}_2$  with a 2 : 1 ratio attributed to water formation. It has been reported that deposition of  $\text{Cr}_2\text{O}_3$  suppresses water formation on noble metal cocatalysts due to covering the noble metal cores with a thin  $\text{Cr}_2\text{O}_3$  layer.<sup>6,48</sup> However, the result indicated that a part of the Pt surface was still exposed after  $\text{Cr}_2\text{O}_3$  deposition. Thus, the cocatalyst survey revealed that the Ru cocatalyst was the most effective cocatalyst among those examined. Gradual decreases in gas evolution rates during Z-WS were observed for all cocatalysts. Although water formation would be one reason for the deactivation in the reaction using  $\text{Cr}_2\text{O}_3$ /Pt/CLTO as described above, reduction of  $\text{O}_2$  over the surface of CLTO and/or exposed cocatalysts mainly caused the deactivation as discussed later. Modification with  $\text{Cr}_2\text{O}_3$  seemed to be not important for the Ru cocatalyst in consideration of the inactivity for water formation. However, remarkable effects of  $\text{Cr}_2\text{O}_3$  deposition were observed in Z-WS (Fig. S6†). Although Z-WS took place even with Ru/CLTO,  $\text{Cr}_2\text{O}_3$ /Ru/CLTO exhibited 8.5 times higher activity than Ru/CLTO.  $\text{Cr}_2\text{O}_3$ /Ru/CLTO also showed higher activity in  $\text{H}_2$  evolution from the  $\text{Co}(\text{bpy})_3\text{SO}_4$  solution (Fig. S7†), which was a half reaction of Z-WS. Thus, the modification with  $\text{Cr}_2\text{O}_3$  was crucial in the present Z-scheme system using the  $\text{Co}(\text{bpy})_3^{3+/2+}$  redox shuttle. CV measurements using bare FTO and  $\text{Cr}_2\text{O}_3$ /FTO clearly proved the significant role of  $\text{Cr}_2\text{O}_3$  (Fig. S8†). The bare FTO showed a pair of reversible currents ascribed to the oxidation and reduction of the Co complex. The current due to the redox of the Co complex was suppressed over the  $\text{Cr}_2\text{O}_3$ /FTO electrode. Thus,  $\text{Cr}_2\text{O}_3$  suppressed the reduction of  $\text{Co}(\text{bpy})_3^{3+}$ , which is an undesired backward reaction in Z-WS. It should be noted that the  $\text{H}_2$  evolution rate in Z-WS was much higher than that in the half reaction. This suggested that the competitive reduction reaction strongly suppressed  $\text{H}_2$  production. In the half reaction,  $\text{Co}(\text{bpy})_3^{3+}$  is simultaneously formed by oxidation of  $\text{Co}(\text{bpy})_3^{2+}$  by holes when electrons are consumed by  $\text{H}_2$  production. If the electrons preferably reduce  $\text{Co}(\text{bpy})_3^{3+}$  rather than  $\text{H}^+$ ,  $\text{H}_2$  evolution should be remarkably suppressed. The reduction of  $\text{Co}(\text{bpy})_3^{3+}$  was possible on the surface of CLTO even after the  $\text{Cr}_2\text{O}_3$  modification. In the Z-scheme system, the coexistent OEP pushes  $\text{Co}(\text{bpy})_3^{3+}$  back to  $\text{Co}(\text{bpy})_3^{2+}$  in addition to  $\text{O}_2$  production and keeps the low quantity of  $\text{Co}(\text{bpy})_3^{3+}$  if the OEP functions well. Thus, Z-WS with  $\text{H}_2$  evolution rates higher than those in the half reaction is possible. Indeed, Abe and coworkers have reported similar phenomena in the  $\text{IO}_3^-/\text{I}^-$ -based Z-scheme system.<sup>27</sup>

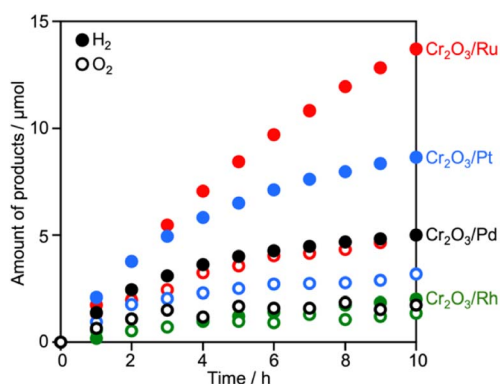


Fig. 2 Z-WS by the  $\text{Cr}_2\text{O}_3$ /M/CLTO- $\text{BiVO}_4$ - $\text{Co}(\text{bpy})_3\text{SO}_4$  system. Photocatalyst: 0.05 g each; reactant solution: 0.1 mM  $\text{Co}(\text{bpy})_3\text{SO}_4$ , 160 mL; light source: 300 W Xe lamp ( $\lambda > 420$  nm).

### Deposition of Ru cocatalysts under different conditions

Deposition conditions were examined for Ru/CLTO because they frequently affect photocatalytic performance.<sup>49,50</sup> In the aforementioned experiments, Ru(10% MeOH)/CLTO prepared by photodeposition in a 10% methanol solution was used. However, the activity of Ru/CLTO for sacrificial  $\text{H}_2$  evolution in 10% methanol was negligible in comparison with that in the reaction using  $\text{Na}_2\text{SO}_3$  and  $\text{Na}_2\text{S}$  (Fig. 1 and S4†). This indicated the poor ability of diluted methanol in scavenging





photogenerated holes in CLTO. The state of photodeposited Ru cocatalysts would be influenced by conditions with different abilities in scavenging holes. Thus, Ru(100% MeOH) and Ru(S<sup>2-</sup>), which were prepared by photodeposition in 100% methanol and a mixed solution of Na<sub>2</sub>S and Na<sub>2</sub>SO<sub>3</sub>, were examined for H<sub>2</sub> evolution from the 10% methanol solution with *in situ* deposition of Cr<sub>2</sub>O<sub>3</sub> and for Z-WS. In H<sub>2</sub> evolution (Fig. 3a), Cr<sub>2</sub>O<sub>3</sub>/Ru(S<sup>2-</sup>)/CLTO showed very low activity (1.8 μmol h<sup>-1</sup>) although its parent Ru(S<sup>2-</sup>)/CLTO produced H<sub>2</sub> with a 402 μmol h<sup>-1</sup> rate from the solution containing Na<sub>2</sub>S and Na<sub>2</sub>SO<sub>3</sub> as shown in Fig. S4.† Cr<sub>2</sub>O<sub>3</sub>/Ru(10% MeOH) and Cr<sub>2</sub>O<sub>3</sub>/Ru(100% MeOH) deposited CLTO showed higher activity than Cr<sub>2</sub>O<sub>3</sub>/Ru(S<sup>2-</sup>)/CLTO by 3.6 and 17.3 times, respectively. In Z-WS (Fig. 3b), Cr<sub>2</sub>O<sub>3</sub>/Ru(10% MeOH) and Cr<sub>2</sub>O<sub>3</sub>/Ru(100% MeOH) produced H<sub>2</sub> and O<sub>2</sub>, and the latter exhibited higher activity. In contrast, Cr<sub>2</sub>O<sub>3</sub>/Ru(S<sup>2-</sup>)/CLTO was inactive. The order of activity in Z-WS showed the same trend as that in H<sub>2</sub> evolution using 10% methanol. Thus, the photodeposition conditions of the Ru cocatalyst gave remarkable differences in photocatalytic activity.

Characterization of Ru/CLTO prepared under different photodeposition conditions was conducted to clarify the differences. Fig. 4a–c show the results of XAFS analysis carried out at the Ru K-edge. The XANES spectra of Ru(10% MeOH) and Ru(100% MeOH) were similar to that of RuO<sub>x</sub>(OH)<sub>y</sub>, whereas the spectrum of Ru(S<sup>2-</sup>)/CLTO was slightly shifted to the low energy side in comparison with that of Ru(10% MeOH). The EXAFS

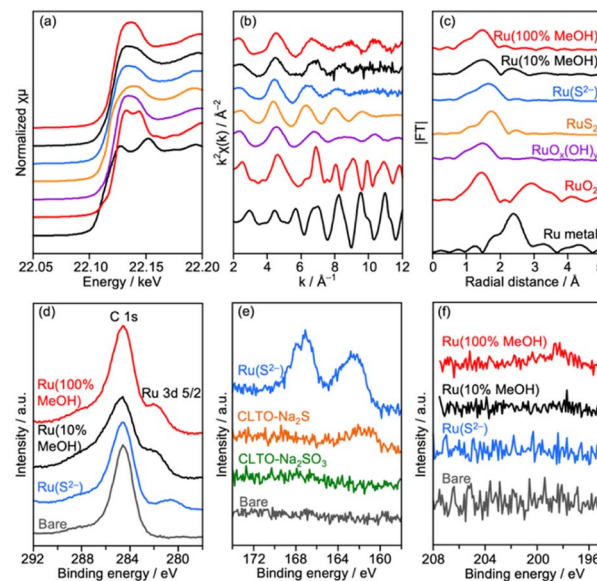


Fig. 4 (a) XANES spectra, (b) EXAFS oscillations, (c) their Fourier transforms and XPS at (d) Ru 3d, (e) S 2p and (f) Cl 2p of Ru/CLTO prepared under different photodeposition conditions.

oscillations of Ru(10% MeOH) and Ru(100% MeOH) appeared to be similar to that of RuO<sub>x</sub>(OH)<sub>y</sub>. On the other hand, Ru(S<sup>2-</sup>) showed different features from RuO<sub>x</sub>(OH)<sub>y</sub> in both XANES and EXAFS. The oscillation period in EXAFS of Ru(S<sup>2-</sup>) was shorter than that of RuO<sub>x</sub>(OH)<sub>y</sub>, resulting in a longer bonding distance than that of RuO<sub>x</sub>(OH)<sub>y</sub> in the Fourier transforms of EXAFS. This EXAFS feature of Ru(S<sup>2-</sup>) was similar to that of RuS<sub>2</sub>. The samples were also analyzed by XPS (Fig. 4d–f). At Ru 3d, Ru(10% MeOH) and Ru(100% MeOH) showed a similar peak at 281.8 eV attributed to RuO<sub>x</sub>(OH)<sub>y</sub>.<sup>50</sup> Ru(S<sup>2-</sup>) showed a peak at 280.6 eV which was remarkably low binding energy in comparison with Ru(10% MeOH) and Ru(100% MeOH). In S 2p, Ru(S<sup>2-</sup>) gave two obvious peaks at 162.0 and 167.6 eV attributed to S<sup>2-</sup> and SO<sub>3</sub><sup>2-</sup> species, respectively. The bare CLTO was treated in solutions of Na<sub>2</sub>S and Na<sub>2</sub>SO<sub>3</sub> in the dark to evaluate the influences of S<sup>2-</sup> and SO<sub>3</sub><sup>2-</sup> upon the CLTO surface. No sulfur signals were observed in the Na<sub>2</sub>SO<sub>3</sub>-treated sample, whereas a weak peak attributed to S<sup>2-</sup> was observed in the Na<sub>2</sub>S-treated sample. Thus, the CLTO surface suffered from partial sulfuration due to its strong affinity to S<sup>2-</sup>. The signal intensity of S<sup>2-</sup> in the Ru(S<sup>2-</sup>) sample was stronger than that in the Na<sub>2</sub>S-treated sample, indicating that the S<sup>2-</sup> signal in Ru(S<sup>2-</sup>) was not due to the sulfurized CLTO surface but the sulfide-like Ru species. In Cl 2p, Ru(100% MeOH) showed a very weak peak whereas Ru(10% MeOH) and Ru(S<sup>2-</sup>) showed no peaks. The results of XAFS and XPS revealed the changes in chemical states of the Ru cocatalyst with the photodeposition conditions; RuO<sub>x</sub>(OH)<sub>y</sub> in Ru(10% MeOH), RuO<sub>x</sub>(OH)<sub>y</sub>Cl<sub>2</sub> in Ru(100% MeOH) and sulfide-like Ru species adsorbing SO<sub>3</sub><sup>2-</sup> in Ru(S<sup>2-</sup>). However, the state of Ru(10% MeOH) and Ru(100% MeOH) could be considered to be almost the same because the Cl content in Ru(100% MeOH) was very low. Ru(100% MeOH) and Ru(S<sup>2-</sup>) as well as Ru(10% MeOH) were also inactive for water formation as depicted in

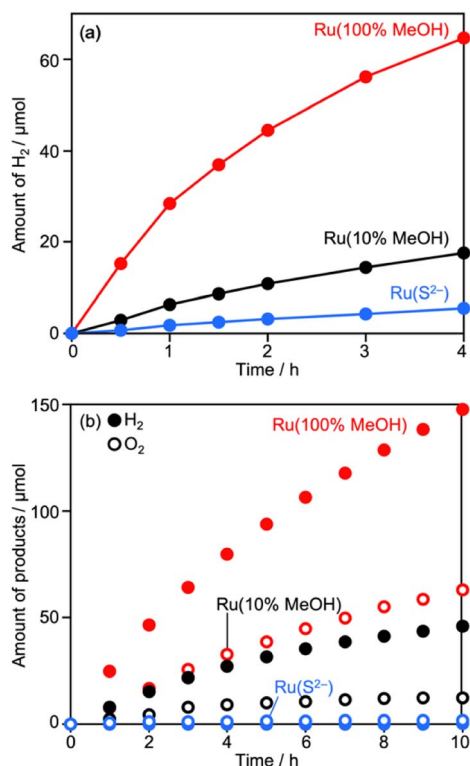


Fig. 3 Photocatalytic (a) H<sub>2</sub> evolution and (b) Z-WS using Cr<sub>2</sub>O<sub>3</sub> (1.2 wt%)/Ru (0.5 wt%)/CLTO prepared under different photodeposition conditions. Photocatalyst: 0.2 g for (a) and 0.05 g each for (b); reactant solution: 10 vol% methanol for (a) and 0.1 mM Co(bpy)<sub>3</sub>SO<sub>4</sub> for (b), 160 mL; light source: 300 W Xe lamp (λ >420 nm).



Fig. S9.† None of the Ru cocatalysts were in the metallic state but oxyhydroxide or sulfide-like states, giving the inactivity for water formation. Thus, the different photocatalytic activities of Ru/CLTO in Z-WS shown in Fig. 3 were not influenced by water formation over the Ru cocatalysts. As described above, XPS analysis revealed that the CLTO surface was partly sulfurized in the  $S^{2-}$  solution. The partly sulfurized surface would be inactive for oxidation of methanol and  $Co(bpy)_3^{2+}$ , resulting in the very low activity of the  $Ru(S^{2-})$  sample as depicted in Fig. 3.

SEM observation was conducted to examine the particle morphology of the photodeposited Ru cocatalysts (Fig. 5). In  $Ru(10\% \text{ MeOH})$  and  $Ru(S^{2-})$ , several tens of nm of particles were deposited on the smooth CLTO surface, and aggregation occurred. In contrast,  $Ru(100\% \text{ MeOH})$  showed a greatly different feature. Large plate objects with 100–200 nm sizes and about 30 nm thickness were deposited in addition to fine particles with 10 nm size. It was suspected that the large plates were caused by damage from photoexcitation in 100% methanol. However, STEM-EDS analysis proved that the plate object did not contain Cu and Ti but Ru (Fig. 6). Thus, the characterization revealed that the Ru species in  $Ru(10\% \text{ MeOH})$  and  $Ru(100\% \text{ MeOH})$  was in a similar chemical state, but  $Ru(100\% \text{ MeOH})$  had the characteristic morphology. The unusually large  $Ru(100\% \text{ MeOH})$  provides two positive factors compared with aggregated fine  $Ru(10\% \text{ MeOH})$ . One is difference in contact between the Ru particle and CLTO. The fine Ru particles loosely deposited on CLTO while the large Ru plates were in close contact on CLTO. Another is the difference in electron migration in the Ru cocatalyst particle. Electrons moved to the Ru cocatalyst poorly migrate in the aggregated fine particles due to the grain boundary, while smooth migration occurs in  $Ru(100\% \text{ MeOH})$  despite the large sizes. The close contact on CLTO and poor grain boundary in  $Ru(100\% \text{ MeOH})$  improved electron extraction from CLTO and electron migration in the Ru cocatalyst, resulting in the highest activity of  $Cr_2O_3/Ru(100\% \text{ MeOH})/CLTO$  in  $H_2$  evolution and Z-WS.

The optimal amount of the  $Ru(100\% \text{ MeOH})$  cocatalyst was investigated for Z-WS (Fig. S10†). Activity was remarkably enhanced as the amount of the Ru cocatalyst increased up to 0.3 wt%. The evolution rate of the 0.5 wt% sample was similar to that of the 0.3 wt% sample in the early stage of the reaction,

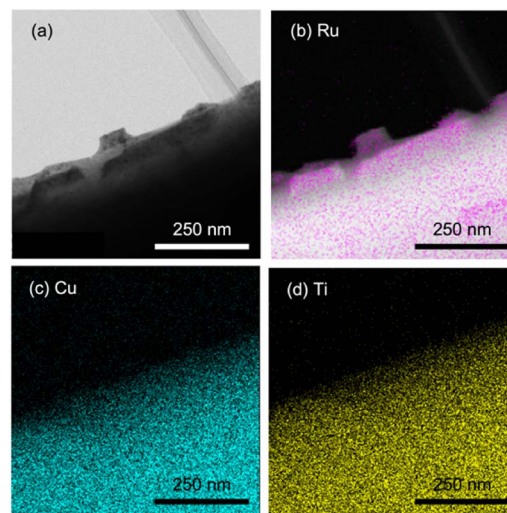


Fig. 6 (a) TEM image and (b–d) STEM-EDS images of  $Ru(100\% \text{ MeOH})/CLTO$ .

however the evolution rate decreased after 3 h of reaction time. Further deposition of Ru (1 wt%) gave lower activity.

Deposition of the Ru cocatalyst was also performed by an impregnation method under three heat-treatment conditions as described in the experimental section. No remarkable changes were seen in XRD for samples treated at 200 °C in  $N_2$  ( $Ru(N_2)$ ) and under vacuum ( $Ru(\text{evac})$ ), while diffraction peaks attributed to metallic Cu obviously appeared after treatment in  $H_2$  at 150 °C ( $Ru(H_2)$ ) despite the relatively low treatment temperature (Fig. S11†). Accordingly, numerous particles with 50–100 nm diameters were observed on the surface of CLTO (Fig. S12†), and these particles seemed to be metallic Cu as proved in XRD analysis. Thus, CLTO underwent the reductive decomposition by  $H_2$  treatment at 150 °C. XAFS analysis revealed that the state of Ru cocatalysts was also changed by the heat treatment conditions (Fig. 7). XANES and EXAFS clarified that metallic Ru was present in the  $Ru(H_2)$  sample while the samples of  $Ru(N_2)$  and  $Ru(\text{evac})$  seemed to be  $RuO_x(OH)_y$  in consideration of the similarity in spectra between the samples and  $RuO_x(OH)_y$ . No remarkable differences were observed in the morphology of the Ru catalyst except for  $Ru(H_2)$  as shown in Fig. S12.†

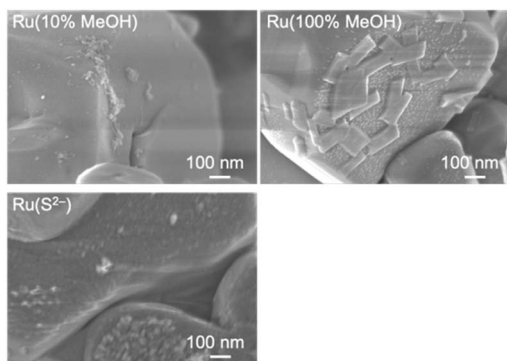


Fig. 5 SEM images of  $Ru/CLTO$  prepared under different photo-deposition conditions.

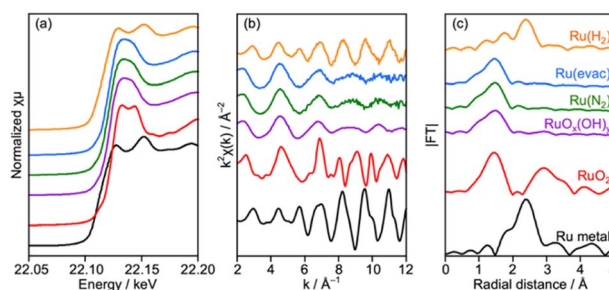


Fig. 7 (a) XANES spectra, (b) EXAFS oscillation and (c) its Fourier transforms analyzed at the Ru K-edge for  $Ru/CLTO$  prepared by the impregnation method under different heat treatment conditions.



The photocatalytic performance of  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO}$  prepared *via* the impregnation method was evaluated for Z-WS after the  $\text{Cr}_2\text{O}_3$  modification (Fig. S13†). The  $\text{Ru}(\text{H}_2)$  sample which suffered from the reductive decomposition was excluded for this evaluation. The  $\text{Ru}(\text{evac})$  and  $\text{Ru}(\text{N}_2)$  samples were also active for Z-WS. Their activities were only comparable with that of the  $\text{Ru}(10\% \text{ MeOH})$  sample prepared by the photodeposition method shown in Fig. 3b. Thus, it has been concluded that the photodeposition in 100% methanol is the best condition for  $\text{Ru}/\text{CLTO}$  to obtain high activity in Z-WS. The STH value of the present Z-WS was determined to be 0.029% using the optimized sample. The  $\text{Ru}(100\% \text{ MeOH})$  samples were used for further experiments.

### Characteristics of the $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO-BiVO}_4$ Z-scheme system

As described above, water splitting was achieved by the combination of  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO}$  and  $\text{BiVO}_4$  in the presence of the  $\text{Co}(\text{bpy})_3^{3+/2+}$  redox shuttle. In the absence of  $\text{Co}(\text{bpy})_3^{3+/2+}$ , water splitting with significant activity was not achieved by the  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO-BiVO}_4$  combination (Fig. 8). It has been reported that RGO-modification facilitates electron transfer from an OEP to HEP in Z-WS without redox couples.<sup>22</sup> Water splitting, indeed, took place with higher gas evolution rates when RGO-modified  $\text{BiVO}_4$  was employed. Nevertheless, its activity was much lower than that of the system using  $\text{Co}(\text{bpy})_3^{3+/2+}$ . The results clearly prove the effectiveness of the  $\text{Co}(\text{bpy})_3^{3+/2+}$  redox shuttle in the present Z-scheme system in spite of the redox couple causing unfavourable backward reactions.

The vital role of the  $\text{Cr}_2\text{O}_3$  modification in the suppression of reduction of  $\text{Co}(\text{bpy})_3^{3+}$  was confirmed for  $\text{Ru}(10\% \text{ MeOH})/\text{CLTO}$  as shown in Fig. S6 and S7.† The activity for Z-WS was remarkably improved when the Ru cocatalyst was changed from  $\text{Ru}(10\% \text{ MeOH})$  to  $\text{Ru}(100\% \text{ MeOH})$ . We investigated the necessity of the  $\text{Cr}_2\text{O}_3$  modification for the highly efficient  $\text{Ru}(100\% \text{ MeOH})$  cocatalyst (Fig. 9a).  $\text{H}_2$  and  $\text{O}_2$  were evolved in the early stage of the reaction even without the  $\text{Cr}_2\text{O}_3$  modification, however the gas evolution stopped soon. In contrast, the sample modified with  $\text{Cr}_2\text{O}_3$  evolved  $\text{H}_2$  and  $\text{O}_2$  with a rate

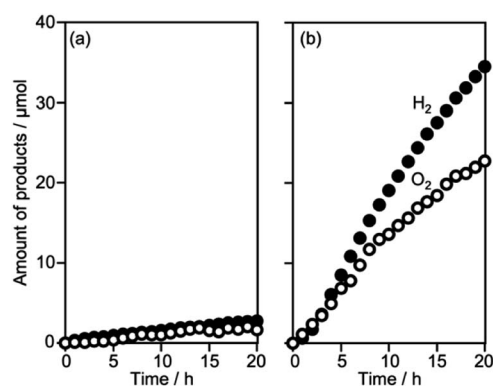


Fig. 8 Time courses of gas evolution by Z-scheme systems without the  $\text{Co}(\text{bpy})_3^{3+/2+}$  electron shuttle; (a)  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO-BiVO}_4$  and (b)  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO-RGO/BiVO}_4$ . Photocatalyst: 0.05 g each; reactant solution: water, 160 mL; light source: 300 W Xe lamp ( $\lambda > 420 \text{ nm}$ ).

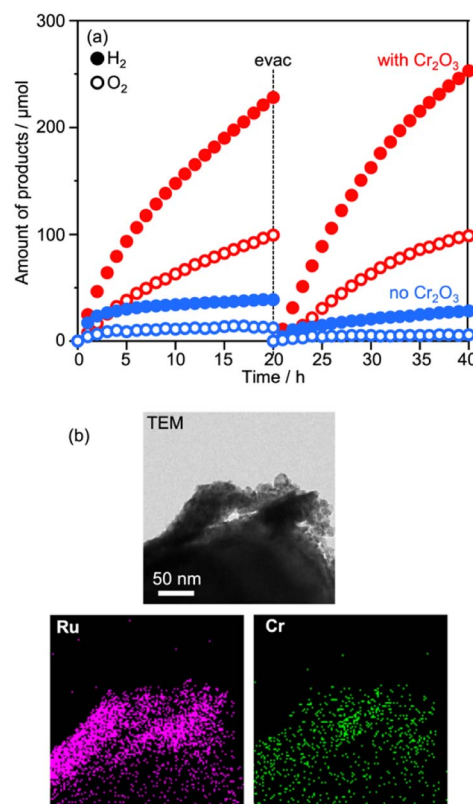


Fig. 9 (a) Influences of  $\text{Cr}_2\text{O}_3$  modification on Z-WS employing  $\text{Ru}(100\% \text{ MeOH})/\text{CLTO}$ . (b) TEM and element mapping images of  $\text{Cr}_2\text{O}_3/\text{Ru}(100\% \text{ MeOH})/\text{CLTO}$ .

higher than that for without  $\text{Cr}_2\text{O}_3$  modification and continued for a long time. It was confirmed that  $\text{Cr}_2\text{O}_3$  was deposited around the Ru particles as shown in Fig. 9b. In the case of  $\text{Ru}/\text{CLTO}$ , reduction of  $\text{Co}(\text{bpy})_3^{3+}$  easily occurred on the Ru cocatalyst. As proved in electrochemical measurements (Fig. S8†), the  $\text{Cr}_2\text{O}_3$  layer hindered  $\text{Co}(\text{bpy})_3^{3+}$  from accessing the Ru cocatalyst as reported for the  $\text{IO}_3^-/\text{I}^-$  system,<sup>45</sup> resulting in higher and stable water splitting. On the other hand, the activity of  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO}$  gradually decreased with the reaction time and recovered in the second run performed after removal of gaseous products. This behaviour indicated that the performance of  $\text{Cr}_2\text{O}_3/\text{Ru}/\text{CLTO}$  did not collapse during the reaction. To check the stability of CLTO, XPS and XRD measurements were performed for the samples after photoirradiation (Fig. S14 and S15†). A new weak peak at 935.1 eV ascribed to  $\text{Cu}^{2+}$  appeared after deposition of  $\text{Ru}(100\% \text{ MeOH})$ . After deposition of  $\text{Cr}_2\text{O}_3$  in 10% methanol, the  $\text{Cu}^{2+}$  peak increased while the  $\text{Cu}^+$  peak at 933.3 eV decreased significantly. The changes in XPS were due to oxidation of  $\text{Cu}^+$  during photoirradiation in 10% methanol. On the other hand, no changes in XRD patterns were seen after deposition of Ru and  $\text{Cr}_2\text{O}_3$ . Moreover, no changes except the presence of  $\text{BiVO}_4$  were observed in XPS and XRD after Z-WS. Thus, sufficient stability of the CLTO crystal was confirmed despite partial oxidation of  $\text{Cu}^+$  at the surface of CLTO. The Z-scheme system consisting of  $\text{Ru}/\text{SrTiO}_3:\text{Rh}$ ,  $\text{BiVO}_4$  and  $\text{Co}(\text{bpy})_3^{3+/2+}$  did not show such deactivation during the



reaction although the same OEP was employed as shown in Fig. S16.† In addition, water formation from H<sub>2</sub> and O<sub>2</sub> did not take place on Ru/CLTO as described before (Fig. S9†). We suspected from these results that the gradual decrease in the activity was due to the reduction of O<sub>2</sub> over Cr<sub>2</sub>O<sub>3</sub>/Ru/CLTO. When 10 kPa of O<sub>2</sub> was introduced into the reaction system instead of Ar, H<sub>2</sub> evolution caused by water splitting was significantly suppressed (Fig. S17†). This indicated that some of the electrons photogenerated in CLTO reacted with O<sub>2</sub> on the exposed Ru cocatalyst and/or the surface of CLTO.

The UV-vis spectra of CLTO, BiVO<sub>4</sub> and SrTiO<sub>3</sub>:Rh are compared in Fig. 10a, where the spectra of monochromatic lights are also shown. CLTO absorbs photons with wavelengths up to 600 nm, which is longer than the absorption edge of SrTiO<sub>3</sub>:Rh (540 nm). To confirm the utilization of long-wavelength photons by CLTO, Z-WS was also examined under irradiation using monochromatic lights with 430 and 560 nm wavelengths (Fig. 10b). Water splitting proceeded under the 430 nm light, and the EQY of the Z-scheme system employing Cr<sub>2</sub>O<sub>3</sub>/Ru/CLTO was determined to be 0.5%. No water splitting was induced in the CLTO system when the 560 nm light was solely used. This is because the Z-scheme mechanism cannot be completed without excitation of BiVO<sub>4</sub>. However, the gas evolution rate was increased when the 560 nm light was added to the basic incident light (430 nm). The additional 560 nm light did not enhance the gas evolution when Ru/SrTiO<sub>3</sub>:Rh was used

as the HEP instead of Cr<sub>2</sub>O<sub>3</sub>/Ru/CLTO (Fig. 10c). The difference in the influence of the additional 560 nm light between CLTO and SrTiO<sub>3</sub>:Rh systems is reasonably explained by the photo absorption properties. The 560 nm light was sufficient to excite CLTO, but insufficient for excitation of SrTiO<sub>3</sub>:Rh. Thus, it was clearly confirmed that excitation of CLTO by long-wavelength photons contributes to Z-WS.

## Conclusions

Utilization of CLTO in the totally visible responsive Z-scheme system based on the Co(bpy)<sub>3</sub><sup>3+/2+</sup> redox shuttle was demonstrated. Modifying CLTO with the Ru cocatalyst and Cr<sub>2</sub>O<sub>3</sub> was effective to achieve Z-WS. The unusually large Ru cocatalyst was discovered to be an efficient cocatalyst more than general fine particles for CLTO. The advantage of CLTO over SrTiO<sub>3</sub>:Rh in the response to longer wavelength light was experimentally confirmed, although the EQY of the present Z-scheme system was limited to 0.5% at 430 nm. The Cr<sub>2</sub>O<sub>3</sub> deposition was crucial to suppressing the reduction of Co(bpy)<sub>3</sub><sup>3+</sup> on Ru/CLTO. However, unfavorable backward reactions and reduction of Co(bpy)<sub>3</sub><sup>3+</sup> and O<sub>2</sub>, still took place. Therefore, the efficiency of the CLTO-BiVO<sub>4</sub> system will be improved by establishing advanced surface modification methods to suppress the backward reactions as well as preparation of fine CLTO particles.

## Author contributions

S. Y. guided the experiments, analyzed the data and wrote the manuscript. T. K., Q. L. and T. Y. performed sample preparation, characterization and photocatalytic experiments. S. N. and H. Ku. performed XAFS measurements and analyses. M. K. performed TEM observation. H. Ka. conceived the idea, supervised the research and wrote the manuscript. All authors discussed and commented on the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was partly supported by KAKENHI from JSPS (Grant Numbers JP17H06438, JP19H02806 and JP20H05085) and the Futaba Foundation. XAFS measurements were performed with the approval of the Photon Factory Program Advisory Committee (Proposal numbers 2020G597 and 2021G597). TEM observation was carried out with the support of the Joint research program of the Institute of Materials and Systems for Sustainability, Nagoya University.

## References

- 1 A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253–278.
- 2 Q. Wang and K. Domen, *Chem. Rev.*, 2020, **120**, 919–985.
- 3 X. Tao, Y. Zhao, S. Wang, C. Li and R. Li, *Chem. Soc. Rev.*, 2022, **51**, 10120–10122.

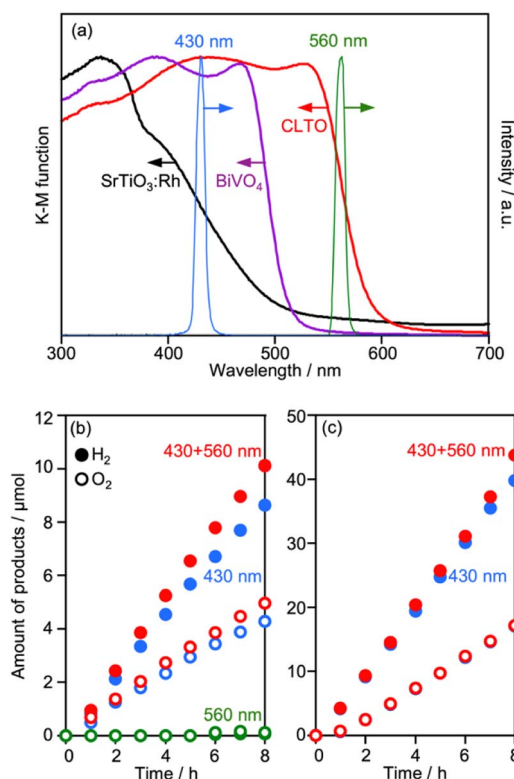


Fig. 10 (a) UV-vis spectra of CLTO, BiVO<sub>4</sub> and SrTiO<sub>3</sub>:Rh reduced by H<sub>2</sub>, and spectra of monochromatic light at 430 and 560 nm. Z-WS in 0.1 mM Co(bpy)<sub>3</sub>SO<sub>4</sub> by (b) Cr<sub>2</sub>O<sub>3</sub>/Ru/CLTO-BiVO<sub>4</sub> and (c) Ru/SrTiO<sub>3</sub>:Rh-BiVO<sub>4</sub> systems under different irradiation conditions.





- 4 H. Kato, K. Asakura and A. Kudo, *J. Am. Chem. Soc.*, 2003, **125**, 3082–3089.
- 5 Y. Sakata, T. Hayashi, R. Yasunaga, N. Yanaga and H. Imamura, *Chem. Commun.*, 2015, **51**, 12935–12938.
- 6 T. Takata, J. Jiang, Y. Sakata, M. Nakabayashi, N. Shibata, V. Nandal, K. Seki, T. Hisatomi and K. Domen, *Nature*, 2020, **581**, 411–414.
- 7 K. Maeda, *ACS Catal.*, 2013, **3**, 1486–1503.
- 8 Y. Wang, H. Suzuki, J. Xie, O. Tomita, D. J. Martin, M. Higashi, D. Kong, R. Abe and J. Tang, *Chem. Rev.*, 2018, **118**, 5201–5241.
- 9 B. Ng, L. K. Putri, X. Y. Kong, Y. W. Teh, P. Pasbakhsh and S. Chai, *Adv. Sci.*, 2020, **7**, 1903171.
- 10 H. Kato, M. Hori, R. Kenta, Y. Shimodaira and A. Kudo, *Chem. Lett.*, 2004, **33**, 1348–1349.
- 11 R. Abe, M. Higashi and K. Domen, *ChemSusChem*, 2011, **4**, 228–237.
- 12 D. J. Martin, P. J. T. Reardon, S. J. A. Moniz and J. Tang, *J. Am. Chem. Soc.*, 2014, **136**, 12568–12571.
- 13 G. Zhao, X. Huang, F. Fina, G. Zhang and J. T. S. Irvine, *Catal. Sci. Technol.*, 2015, **5**, 3416–3422.
- 14 S. Chen, Y. Qi, T. Hisatomi, Q. Ding, T. Asai, Z. Li, S. S. K. Ma, F. Zhang, K. Domen and C. Li, *Angew. Chem., Int. Ed.*, 2015, **54**, 8498–8501.
- 15 Q. Wang, T. Hisatomi, Y. Suzuki, Z. Pan, J. Seo, M. Katayama, T. Minegishi, H. Nishiyama, T. Takata, K. Seki, A. Kudo, T. Yamada and K. Domen, *J. Am. Chem. Soc.*, 2017, **139**, 1675–1683.
- 16 A. Nakada, H. Suzuki, J. J. M. Vequizo, K. Ogawa, M. Higashi, A. Saeki, A. Yamakata, H. Kageyama and R. Abe, *ACS Appl. Mater. Interfaces*, 2019, **11**, 45606–45611.
- 17 S. Nishioka, K. Yanagisawa, D. Lu, J. J. M. Vequizo, A. Yamakata, K. Kimoto, M. Inada and K. Maeda, *Sustainable Energy Fuels*, 2019, **3**, 2337–2346.
- 18 X. Guan, L. Tian, Y. Zhang, J. Shi and S. Shen, *Nano Res.*, 2023, **16**, 4568–4573.
- 19 R. Kenta, T. Ishii, H. Kato and A. Kudo, *J. Phys. Chem. B*, 2004, **108**, 8992–8995.
- 20 A. Kudo, K. Omori and H. Kato, *J. Am. Chem. Soc.*, 1999, **121**, 11459–11467.
- 21 Y. Sasaki, H. Nemoto, K. Saito and A. Kudo, *J. Phys. Chem. C*, 2009, **113**, 17536–17542.
- 22 A. Iwase, Y. H. Ng, Y. Ishiguro, A. Kudo and R. Amal, *J. Am. Chem. Soc.*, 2011, **133**, 11054–11057.
- 23 Y. Sasaki, H. Kato and A. Kudo, *J. Am. Chem. Soc.*, 2013, **135**, 5441–5449.
- 24 Q. Jia, A. Iwase and A. Kudo, *Chem. Sci.*, 2014, **5**, 1513–1519.
- 25 Q. Wang, T. Hisatomi, Q. Jia, H. Tokudome, M. Zhong, C. Wang, Z. Pan, T. Takata, M. Nakabayashi, N. Shibata, Y. Li, I. D. Sharp, A. Kudo, T. Yamada and K. Domen, *Nat. Mater.*, 2016, **15**, 611–615.
- 26 T. Hisatomi, K. Takanabe and K. Domen, *Catal. Lett.*, 2015, **145**, 95–108.
- 27 M. Higashi, R. Abe, T. Takata and K. Domen, *Chem. Mater.*, 2009, **21**, 1543–1549.
- 28 M. Tabata, K. Maeda, M. Higashi, D. Lu, T. Takata, R. Abe and K. Domen, *Langmuir*, 2010, **26**, 9161–9165.
- 29 W. Wang, J. Chen, C. Li and W. Tian, *Nat. Commun.*, 2014, **5**, 4647.
- 30 W. Zhao, K. Maeda, F. Zhang, T. Hisatomi and K. Domen, *Phys. Chem. Chem. Phys.*, 2014, **16**, 12051–12056.
- 31 K. Iwashina, A. Iwase, S. Nozawa, S. Adachi and A. Kudo, *Chem. Mater.*, 2016, **28**, 4677–4685.
- 32 R. Kobayashi, T. Takashima, S. Tanigawa, S. Takeuchi, B. Ohtani and H. Irie, *Phys. Chem. Chem. Phys.*, 2016, **18**, 27754–27760.
- 33 H. Fujito, H. Kunioku, D. Kato, H. Suzuki, M. Higashi, H. Kageyama and R. Abe, *J. Am. Chem. Soc.*, 2016, **138**, 2082–2085.
- 34 Z. Pan, T. Hisatomi, Q. Wang, S. Chen, A. Iwase, M. Nakabayashi, N. Shibata, T. Takata, M. Katayama, T. Minegishi, A. Kudo and K. Domen, *Adv. Funct. Mater.*, 2016, **26**, 7011–7019.
- 35 A. Iwase and A. Kudo, *Chem. Commun.*, 2017, **53**, 6156–6159.
- 36 T. Hisatomi, T. Yamamoto, Q. Wang, T. Nakanishi, T. Higashi, M. Katayama, T. Minegishi and K. Domen, *Catal. Sci. Technol.*, 2018, **8**, 3918–3925.
- 37 S. Sun, T. Hisatomi, Q. Wang, S. Chen, G. Ma, J. Liu, S. Nandy, T. Minegishi, M. Katayama and K. Domen, *ACS Catal.*, 2018, **8**, 1690–1696.
- 38 A. Kudo, S. Yoshino, T. Tsuchiya, Y. Udagawa, Y. Takahashi, M. Yamaguchi, I. Ogasawara, H. Matsumoto and A. Iwase, *Faraday Discuss.*, 2019, **215**, 313–328.
- 39 H. Kumagai, R. Aoyagi, K. Kato, A. Yamakata, M. Kakihana and H. Kato, *ACS Appl. Energy Mater.*, 2021, **4**, 2056–2060.
- 40 S. Yoshino, T. Takayama, Y. Yamaguchi, A. Iwase and A. Kudo, *Acc. Chem. Res.*, 2022, **55**, 966–977.
- 41 A. Iwase, R. Sakamoto and H. Misono, *Chem. Commun.*, 2022, **58**, 12951–12954.
- 42 H. Kato, T. Fujisawa, M. Kobayashi and M. Kakihana, *Chem. Lett.*, 2015, **44**, 973–975.
- 43 R. Abe, K. Sayama and H. Arakawa, *Chem. Phys. Lett.*, 2003, **371**, 360–364.
- 44 H. Kato, Y. Sasaki, A. Iwase and A. Kudo, *Bull. Chem. Soc. Jpn.*, 2007, **80**, 2457–2464.
- 45 Y. Qi, S. Chen, J. Cui, Z. Wang, F. Zhang and C. Li, *Appl. Catal., B*, 2018, **224**, 579–585.
- 46 Y. Mieseki and K. Sayama, *Chem. Commun.*, 2018, **54**, 2670–2673.
- 47 H. P. Duong, T. Mashiyama, M. Kobayashi, A. Iwase, A. Kudo, Y. Asakura, S. Yin, M. Kakihana and H. Kato, *Appl. Catal., B*, 2019, **252**, 222–229.
- 48 K. Maeda, K. Teramura, D. Lu, N. Saito, Y. Inoue and K. Domen, *Angew. Chem., Int. Ed.*, 2006, **45**, 7806–7809.
- 49 Y. Sasaki, A. Iwase, H. Kato and A. Kudo, *J. Catal.*, 2008, **259**, 133–137.
- 50 H. Suzuki, S. Nitta, O. Tomita, M. Higashi and R. Abe, *ACS Catal.*, 2017, **7**, 4336–4343.

