

Cite this: *Mater. Adv.*, 2021,  
2, 1328

# Distortion induced structural characteristics of $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$ (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb and Lu) double perovskites and their multifunctional optical properties for lighting and ratiometric temperature sensing†

Sariga C. Lal, Jawahar Isuhak Naseemabeevi and Subodh Ganesanpotti \*

Group theoretical predictions obtained from Raman and IR spectra emphasize the structures of B-site ordered double perovskites  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) with ubiquitous  $\text{BO}_6$  or  $\text{B}'\text{O}_6$  octahedral tilting are monoclinic ( $P2_1/n$ ), which was further confirmed via the Rietveld refinement of XRD patterns. The wide band gaps of these compounds were consistent with their ability to absorb UV radiation and hence their potential to act as photoluminescent host materials. Photoluminescence spectra of  $\text{Eu}^{3+}$ -activated  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$ , irrespective of substitution at A- or B-sites, yielded a dominant magnetic dipole transition at 592 nm and a less intense electric dipole transition at 610 nm when excited at 276 nm suggested the preference of  $\text{Eu}^{3+}$  ions to occupy  $\text{Y}^{3+}$  sites. The thermal activation energy of the  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  phosphor was 0.15 eV and its relative sensitivity in the temperature range 300–500 K was estimated to have a maximum of  $0.18\% \text{ K}^{-1}$  at 300 K for FIR measurements, which is better than its decay lifetime counterpart. The red shift and the peak broadening of the high-energy Raman modes at elevated temperatures of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  are due to enhanced B-site octahedral distortions and are correlated with the thermal quenching of  $\text{Eu}^{3+}$  emission. Temperature-dependent lifetimes in the range 80–500 K imply intensification of non-radiative relaxation within the limit. Furthermore, the phosphorescence lifetime, color parameters, and JuddOfelt parameters are explained in detail. The multifunctional optical properties of this phosphor can thus be utilized for technological applications, such as solid-state lighting and ratiometric optical thermometry.

Received 1st July 2020,  
Accepted 8th December 2020

DOI: 10.1039/d0ma00471e

rsc.li/materials-advances

## Introduction

Among the different structural families of ceramic compounds, perovskites ( $\text{ABX}_3$ ) form the most often encountered materials since they are well known for their technological applications owing to their physical and chemical properties.<sup>1</sup> The ideal cubic perovskite structure has a twelve-coordinated A-site cation, a six-coordinated B-site cation and an anion. The perovskite family can be extended by substituting cations at either A- or B-sites to form complex perovskites or double perovskites with the general formulae  $\text{A}_2\text{BB}'\text{X}_6$ ,  $\text{AA}'\text{BB}'\text{X}_6$  and  $\text{AA}'\text{B}_2\text{X}_6$ , where the anion site is usually occupied by oxygen.<sup>1–4</sup> Cationic substitution may cause expansion/contraction or tilting of the  $\text{BX}_6$  octahedra in order to compensate for the

mismatch in ionic radii of the cations and hence, the symmetry of these compounds reduces to tetragonal, monoclinic, trigonal, *etc.* Amongst the quaternary perovskites, the B-site ordered  $\text{A}_2\text{BB}'\text{O}_6$  arouse particular attention among researchers and have been extensively studied for their intriguing structure-dependent properties. Double perovskites with cationic substitution in the B-sites usually adopt 1 : 1 rock salt ordering, where B and B' cations alternate in all three dimensions. The possibility of different cations at the B-site allows novel combinations of elements, including transition metals, lanthanides, actinides and some main group elements. The cation substitution may cause structural alterations, which result in symmetry changes from aristotype cubic ( $Fm\bar{3}m$ ) to hettotypes such as tetragonal ( $I4/m$ ), rhombohedral ( $R\bar{3}$ ) or monoclinic ( $P2_1/n$  or  $I2/m$ ). Moreover, the B-site ordered double perovskites exhibit interesting magnetic, optical, and dielectric as well as superconducting properties.<sup>5–11</sup>

Extensive reviews have been carried out on B-site ordered double perovskites, exploring their structural and physical

Department of Physics, University of Kerala, Thiruvananthapuram, Kerala, India.  
E-mail: Indiasubodh@gmail.com

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ma00471e



properties.<sup>1–3</sup> Several types of inter-lanthanide perovskites showing remarkable physical properties, for example magnetic and optical properties, which can be attributed to the deeplying 4f electrons of the rare earth ions, were discovered in the 1960s.<sup>12,13</sup> These perovskites also have potential applications in the field of solid oxide fuel cells when doped with bivalent ions. In addition, perovskites containing lanthanides have been probed for their properties and applications.<sup>13</sup> Later, in 2017, Kong and Cava<sup>14</sup> reported the crystal structure and magnetic properties of the double perovskites  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, La, Pr, ..., Lu). The crystal structure was reported to be cubic. However, our group<sup>15</sup> re-examined the crystal symmetry of five of these double perovskites  $\text{Ba}_2\text{Ln}_{2/3}\text{TeO}_6$  (Ln = La, Pr, Nd, Sm and Eu) using Raman spectroscopy and Rietveld refinement of the XRD patterns and found that the most likely space group is  $P2_1/n$  with monoclinic symmetry. Moreover, their optical properties were also investigated, and a red-emitting phosphor  $\text{Ba}_2\text{La}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  was also developed in anticipation of using it in white light emitting diodes.

Phosphor-converted white light emitting diodes (WLEDs) are considered to be the next generation of lighting sources.<sup>16–21</sup> However, the deficient emission in the red spectral region results in a low color rendering index (CRI) for these WLEDs. In order to improve the performance of WLEDs, highly efficient and stable red phosphors are usually incorporated.<sup>22–34</sup> Phosphor-converted red emitting LEDs have been a breakthrough in plant cultivation research, since red and far red light serve important functions in photosynthesis as well as in photomorphogenesis.<sup>35</sup> Optical thermometry based on rare earth ion doped oxides is a promising method to gather large-scale imaging and contactless measurement of temperature compared to other conventional thermometers.<sup>36</sup> Recently, optical thermometry has become a major research interest owing to its fast response time, contactless measurement, high precision and accuracy, high signal yield, *etc.* Optical temperature sensing is based on measuring the change in emission intensity against temperature when interacting with physical systems. There are several parameters of luminescence, such as intensity, spectrum bandwidth, spectral shift and lifetime, that can be used to calculate the temperature change, among which measuring the fluorescence intensity ratio (FIR) is the most favourable technique.<sup>36</sup> Trivalent rare earth ion doped systems are used for optical thermometric applications due to the abundant 4f energy levels of these ions. Among the different rare earth ions,  $\text{Eu}^{3+}$  ions, owing to their thermally coupled energy levels (TCLs)  $^5\text{D}_1$  and  $^5\text{D}_0$ , are also used for optical thermometry applications.<sup>37</sup> Therefore, it is essential to synthesize and characterize novel red phosphors that can be used in various technological applications.

Rare earth doped red phosphors require a suitable host matrix that has good absorbance in the near UV region and excellent thermal and chemical stability. Double perovskites are among such host materials for luminescent centers or so-called activator ions. Red phosphors based on rare earth substituted complex perovskites are widely reported for lighting applications.<sup>38–47</sup> In addition, several double perovskite

phosphors,  $\text{Gd}_2\text{ZnTiO}_6:\text{Pr}^{3+}$ ,  $\text{Y}_2\text{MgTiO}_6:\text{Mn}^{4+}$ ,  $\text{LiLaMgWO}_6:\text{Er}^{3+}$ , *etc.*, have been explored for their temperature-sensing potential.<sup>45–47</sup>

In the present work, we successfully synthesized  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) double perovskites and their crystal structure is examined by XRD, Raman and FTIR spectroscopy with B-site substitution of rare earth ions. The previously reported  $\text{Ba}_2\text{Ln}_{2/3}\text{TeO}_6$  (Ln = La, Pr, Nd, Sm and Eu) show no symmetry variation when the B-site is substituted with  $\text{La}^{3+}$  to  $\text{Eu}^{3+}$ . However, the total number of modes in the Raman spectra decrease from 21 to 16 when the B-site changes from  $\text{La}^{3+}$  to  $\text{Eu}^{3+}$ . In addition to this, the tilting or distortion of the  $\text{BO}_6$  and  $\text{B}'\text{O}_6$  octahedra also reduces and the B–O–B' (B = La, Pr, Nd, Sm, Eu; B' = Te) bond angle approaches  $180^\circ$  with B-site variation.<sup>15</sup> This gives an intuition of a possible change in symmetry for  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) from monoclinic to cubic when the B-site undergoes substitution from  $\text{Gd}^{3+}$  to  $\text{Lu}^{3+}$ . The photoluminescence properties of both A- and B-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$ , temperature-dependent luminescence, optical thermometric parameters, photoluminescence decay curves and Judd–Ofelt theory are discussed in detail. This is carried out on the assumption that, unlike  $\text{Ba}_2\text{La}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  which was previously reported,  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  shows enhanced luminescence performance as yttrium-based host matrices like  $\text{Y}_2\text{O}_3:\text{Eu}^{2+}$  have been established as potential red phosphors that can be excited using ultraviolet (UV) radiation due to their wide band gap characteristics (4.6–4.8 eV) and hence utilized in the field of light emitting diode applications.

## Materials and methods

### Synthesis procedure

$\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) double perovskites were synthesized *via* a solid-state ceramic route.  $\text{BaCO}_3$  (Sigma Aldrich,  $\geq 99\%$ ),  $\text{Y}_2\text{O}_3$  (Alfa Aesar, 99.99%),  $\text{Gd}_2\text{O}_3$  (Sigma Aldrich, 99.9%),  $\text{Tb}_4\text{O}_7$  (Sigma Aldrich, 99.9%),  $\text{Dy}_2\text{O}_3$  (Aldrich, 99.9%),  $\text{Ho}_2\text{O}_3$  (Sigma Aldrich,  $\geq 99.9\%$ ),  $\text{Er}_2\text{O}_3$  (Alfa Aesar, 99.9%),  $\text{Tm}_2\text{O}_3$  (Alfa Aesar, 99.997%),  $\text{Yb}_2\text{O}_3$  (Alfa Aesar, 99.9%),  $\text{Lu}_2\text{O}_3$  (Alfa Aesar, 99.9%), and  $\text{TeO}_2$  (Sigma Aldrich,  $\geq 99\%$ ) were the starting materials used. Stoichiometric amounts of the powders were weighed and mixed together in acetone medium by ball milling with ceria-stabilized zirconia balls for 18 h. The slurries of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Dy}_{2/3}\text{TeO}_6$  were calcined at  $1000^\circ\text{C}$  for 20 h and those of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$ ,  $\text{Ba}_2\text{Tb}_{2/3}\text{TeO}_6$ ,  $\text{Ba}_2\text{Ho}_{2/3}\text{TeO}_6$ , and both A- and B-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  (2.5, 5, 7.5, 10, 12.5, 15, 17.5 and 20 mol%) were calcined at  $1200^\circ\text{C}$  for 20 h whereas  $\text{Ba}_2\text{Er}_{2/3}\text{TeO}_6$ ,  $\text{Ba}_2\text{Tm}_{2/3}\text{TeO}_6$ ,  $\text{Ba}_2\text{Yb}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  were calcined at  $1300^\circ\text{C}$  for 20 h. A slow heating rate ( $1^\circ\text{C min}^{-1}$ ) was applied to oxidize  $\text{Te}^{4+}$  to  $\text{Te}^{6+}$ .

### Characterization techniques

X-ray diffractograms were collected using a Bruker D8 Advance diffractometer (40 kV, 40 mA) equipped with a Cu-K $\alpha$  source



( $\lambda = 1.5406 \text{ \AA}$ ), a nickel filter and a Lynx eye position sensitive detector. Topas 4.2 software was used to perform the Rietveld refinement of the XRD patterns. A Chebychev polynomial was used to fit the background. Cell parameters, atomic coordinates, occupancy and isotropic temperature factors were refined. An Ametek EDAX – Octane Plus system was used to carry out EDS analysis. Room temperature micro Raman scattering spectra were recorded using a LABRAM HR-800 Raman spectrometer with a 633 nm He-Ne laser (5 mW) with a resolution of  $1 \text{ cm}^{-1}$ . The FTIR spectra of the samples in the far-IR and mid-IR range were recorded by the ATR method in vacuum using a JASCO FTIR 6800 spectrometer. In the mid-IR region ( $400\text{--}1000 \text{ cm}^{-1}$ ), a Ge-KBr beam splitter and triglycerine sulfate (TGS) detector and in the far-IR region ( $50\text{--}630 \text{ cm}^{-1}$ ), a Myla beam splitter and a polyethylene triglycerine sulfate (PE-TGS) detector were used. The diffuse reflectance spectra were obtained in the range 190–900 nm using a JASCO V-750 UV-Vis spectrophotometer. A Fluorolog spectrofluorometer with a 450 W xenon lamp was used to record the photoluminescence excitation (PLE) and emission (PL) spectra (slit width 1 nm, integration time 0.5 s). The temperature-dependent photoluminescence and lifetime measurements were collected using a cryostat designed by Oxford Instruments attached with a FLS 1000 spectrophotometer from Edinburgh Instruments in a temperature range of 80–500 K. Decay curves were recorded with a flash lamp frequency of 25 Hz with a time range of 40 ms and maximum peak counts of 10 000. Temperature-dependent

Raman spectra were recorded using a Horiba Jobin Yvon LABRAM HR-evolution Raman spectrometer with a 785 nm high-power single-frequency diode laser (90 mW). Quantum yield was measured with the aid of a Quanta- $\phi$  integrating sphere set-up associated with a Fluorolog spectrofluorometer using a 450 W xenon lamp.

## Results and discussion

### XRD patterns of $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$ (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu)

X-ray diffraction technique was used to analyse the crystallinity and phase purity of all the calcined powders. Fig. 1a shows the XRD patterns of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) indexed with pseudocubic lattice planes. XRD patterns of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  are shown separately in Fig. S1 and S2 (ESI<sup>†</sup>). For double perovskites, if the charge difference is  $\geq 2$  and the size difference is greater than  $0.1 \text{ \AA}$ , then the most favourable ordering among the B-site cations is rocksalt ordering. For  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$ , the charge difference between  $\text{R}^{3+}$  and  $\text{Te}^{6+}$  is +3 and the size difference is greater than  $0.1 \text{ \AA}$ , denoting a possible rocksalt ordering of B-site cations. The characteristic R point 111 reflection around  $2\theta \approx 18^\circ$  also indicates the 1:1 rocksalt ordering of these compounds. The splitting of reflections at 440 planes in  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  shown in Fig. 1b and c points

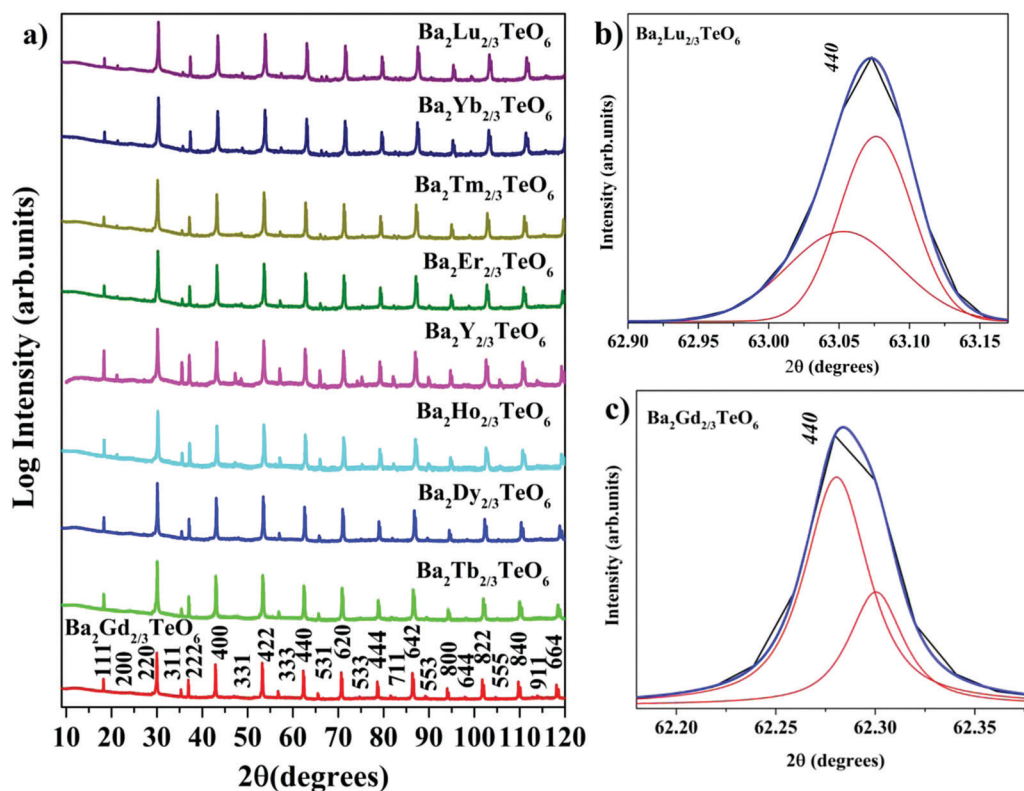


Fig. 1 (a) The combined XRD patterns of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu). (b) The splitting of the 440 planes of  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  and (c)  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$ .







Fig. 3 (a) Room-temperature Raman spectra of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  ( $\text{R} = \text{Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu}$ ). Deconvoluted Raman spectra of (b)  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  and (c)  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$ .

The  $\nu_1$  modes due to the symmetric oxygen stretching vibrations are located in the region  $750\text{--}800\text{ cm}^{-1}$  and the  $\nu_2$  modes due to the asymmetric oxygen stretching vibrations of the octahedra are located in the region  $550\text{--}740\text{ cm}^{-1}$ , whereas the vibrational bands due to the oxygen bending motion of the octahedra are observed in the region  $350\text{--}510\text{ cm}^{-1}$ . The low-energy external modes in the range  $100\text{--}350\text{ cm}^{-1}$  are due to translational and librational modes, which are sensitive to lowering of symmetry due to octahedral tilting. Octahedral distortions are evident from the presence of low-energy modes. For modes above  $650\text{ cm}^{-1}$ , a significant shift to the longer wavenumber region (Fig. S16, ESI<sup>†</sup>) is noticed with a decrease in the ionic radii of the B-site cation from  $\text{Gd}^{3+}$  to  $\text{Lu}^{3+}$ . As the unit cell gets contracted with the substitution of less massive ions, the ionic bonds become stronger and thus more energy is needed for the vibrations of the molecules.

Based on group theoretical calculations, there are 12 different space groups possible for double perovskites with 1 : 1 B-site ordering combined with octahedral tilting. For  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  ( $\text{R} = \text{Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu}$ ), there are more than four modes and hence, among the 12 space groups, the possible symmetries for  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  ( $\text{R} = \text{Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu}$ ) are  $P4_2/n$ ,  $P4/mnc$  and  $I4/m$  (tetragonal) and  $C2/c$  and  $P2_1/n$  (monoclinic). Group theory predicts nine Raman active modes for tetragonal ( $I4/m$ ) and  $P4_2/n$  has 35 Raman active modes, among which 17 are low-energy lattice modes.

In addition, this space group is ascribed to double perovskites with Jahn–Teller ions like  $\text{Mn}^{3+}$ ,  $\text{Ni}^{3+}$  or  $\text{Cu}^{3+}$  as in the case of  $\text{Sr}_2\text{MnWO}_6$ <sup>48</sup> and  $\text{Sr}_2\text{MnMoO}_6$ .<sup>49</sup> The space groups  $P4/mnc$  has 14 Raman active modes and  $C2/c$  has 27 Raman active

modes. However, these space groups can be ruled out since the Rietveld refinement parameters are not reliable compared to the space group  $P2_1/n$ . Thus, in accordance with the previously reported evidences and confirmation of the symmetry of  $\text{Ba}_2\text{Ln}_{2/3}\text{TeO}_6$  ( $\text{Ln} = \text{La, Pr, Nd, Sm}$  and  $\text{Eu}$ ), the most likely symmetry of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  ( $\text{R} = \text{Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu}$ ) is found to be monoclinic ( $P2_1/n$ ). The monoclinic ( $P2_1/n$ ) symmetry is a combination of in-phase and anti-phase tilting of the  $\text{BO}_6$  and  $\text{B}'\text{O}_6$  octahedra around the 001 axes of the ideal cubic structure. The irreducible representation of  $P2_1/n$  space group is given by

$$\Gamma = T(3A_g + 3B_g) + L(3A_g + 3B_g) + \nu_1(A_g + B_g) + \nu_2(2A_g + 2B_g) + \nu_3(3A_g + 3B_g) \quad (1)$$

Thus, there are 24 Raman active modes possible for a double perovskite that crystallizes in monoclinic ( $P2_1/n$ ) symmetry. The absence of other bands predicted by group theory might be due to the polycrystallinity of the compounds, the weak bands which could not be identified among the background noise and some modes may fall outside the range of the spectrum.

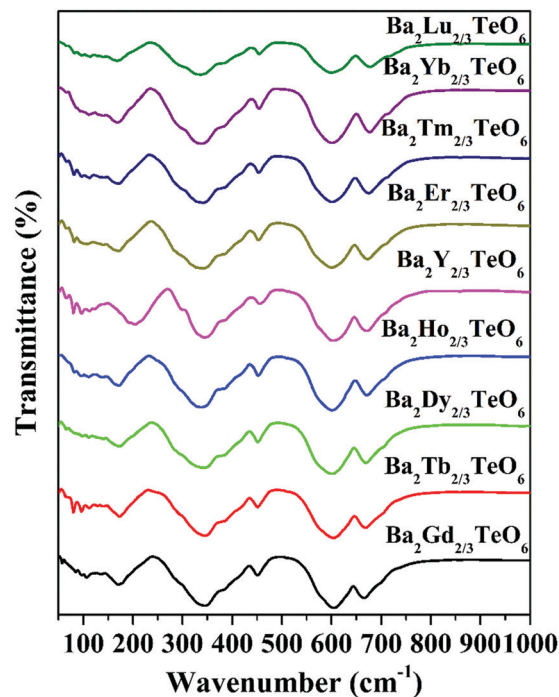
The IR transmittance spectra obtained using the ATR method are shown in Fig. 4. The spectra look almost identical and their visual inspection shows six well-defined modes. A careful inspection of the IR spectra indicates the presence of additional bands and the exact number of modes can only be identified by fitting the IR reflectivity spectra. However, group theory predicts 33 infrared active modes for a monoclinic structure belonging to the  $P2_1/n$  space group. Strong vibration coupling exists between the  $\text{BO}_6$  and  $\text{B}'\text{O}_6$  octahedral moieties.



Table 1 Raman modes of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu)

Compound	Internal			External <i>T</i> or <i>L</i> ( $\text{cm}^{-1}$ )
	$\nu_1$ ( $\text{cm}^{-1}$ )	$\nu_2$ ( $\text{cm}^{-1}$ )	$\nu_3$ ( $\text{cm}^{-1}$ )	
$\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$	771	603	377	80
		651	400	106
		696	457	142
		723		182
				261
				288
$\text{Ba}_2\text{Tb}_{2/3}\text{TeO}_6$	770	602	384	109
		657	401	149
		698	457	183
		715		192
				268
				290
$\text{Ba}_2\text{Dy}_{2/3}\text{TeO}_6$	770	600	377	72
		700	401	109
		724	460	141
				161
				190
				237
$\text{Ba}_2\text{Ho}_{2/3}\text{TeO}_6$	772	602	387	69
		702	403	113
		718	460	155
				155
				155
				155
$\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$	771	596	384	79
		702	405	111
		725	465	144
				171
				194
				225
$\text{Ba}_2\text{Er}_{2/3}\text{TeO}_6$	772	598	366	65
		703	401	111
		718	458	176
			481	196
				265
				289
$\text{Ba}_2\text{Tm}_{2/3}\text{TeO}_6$	769	600	388	111
		705	403	158
		713	460	196
				264
				296
				296
$\text{Ba}_2\text{Yb}_{2/3}\text{TeO}_6$	766	607	373	64
		706	401	112
		726	458	156
				112
				156
				196
$\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$	768	595	383	64
		707	402	295
		722	458	113
				155
				201
				260

The six-coordinated octahedral units with a charge difference of +3 consist of B–O and B'–O bonds which are stronger than the

Fig. 4 FTIR spectra of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu).

twelve coordinated A–O bonds. This simple argument proves that the isolated octahedral groupings will dominate the vibrations in infrared as well as in Raman spectroscopy. Among the 6 well-defined modes, two modes around  $340\text{ cm}^{-1}$  and  $605\text{ cm}^{-1}$  are dominant, which can be assigned to the deformational modes and the antisymmetric stretching vibrations of the  $\text{BO}_6$  octahedral moieties, respectively. All vibrational modes located in the ranges  $150\text{--}175\text{ cm}^{-1}$ ,  $180\text{--}220\text{ cm}^{-1}$ ,  $325\text{--}350\text{ cm}^{-1}$ ,  $450\text{--}500\text{ cm}^{-1}$ ,  $592\text{--}610\text{ cm}^{-1}$  and  $660\text{--}680\text{ cm}^{-1}$  essentially come from the vibrations of  $\text{RO}_6$  and  $\text{TeO}_6$  octahedra. Similar to Raman spectra, the modes above  $590\text{ cm}^{-1}$  show a spectral shift towards the high wavenumber region with lanthanide contraction.

The translational symmetry elements, such as glide planes and screw axes, give rise to systematic absences/extinctions of some (*hkl*) reflections in the XRD patterns. The systematic absences of (*hkl*) reflections, such as (*h0l*) with  $h + l = 2n + 1$  and (*0k0*) with  $k = 2n + 1$ , in the XRD patterns implies the monoclinic symmetry ( $P2_1/n$ ) of the crystals. The presence of the (*330*) reflection for atomic displacement and (*204*) and (*404*) reflections for in-phase tilting also suggest monoclinic symmetry. The refined XRD patterns of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  are shown in Fig. 5a and b. The Rietveld refinement parameters of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  are given in Table 2. From the refined results,  $\beta$  is close to  $90^\circ$ , suggesting the possibility of a structural transition to orthorhombic along with the lanthanide contraction. Among the 12 different space groups predicted by Howard, only *pnmn* belongs to orthorhombic. Very few reports have been published about ordered double perovskites with octahedral tilting belonging to the space group *pnmn*. This space group does not permit the splitting of (*hhh*) reflections which we





Fig. 5 The Rietveld refinement of the XRD patterns of (a)  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and (b)  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$ . The insets show the crystal structures of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$ .

Table 2 Refined crystallographic parameters of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Gd and Lu)

$\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$						
$a = 5.9538(9) \text{ \AA}$	$b = 5.9905(2) \text{ \AA}$	$c = 8.4658(3) \text{ \AA}$	$\beta = 90.0129^\circ$			
$R_{\text{exp}} = 1.95\%$	$R_{\text{wp}} = 4.99\%$	$R_{\text{p}} = 3.76\%$	GOF = 2.56			
Ion	Wyckoff site	x	y	z	Occupancy	$B_{\text{eq}} (\text{\AA}^2)$
Ba	4e	0.487(4)	0.546(2)	0.254(7)	1	0.85(1)
Gd	2d	0.5	0	0	0.667	0.40(5)
Te	2c	0	0.5	0	1	0.40(5)
O1	4e	0.215(5)	0.251(5)	0.018(1)	1	0.98(8)
O2	4e	0.200(5)	0.771(1)	0.004(5)	1	0.98(2)
O3	4e	0.534(2)	0.016(6)	0.264(3)	1	0.97(3)
$\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$						
$a = 5.8894(5) \text{ \AA}$	$b = 5.8998(6) \text{ \AA}$	$c = 8.3329(7) \text{ \AA}$	$\beta = 90.0105^\circ$			
$R_{\text{exp}} = 2.12\%$	$R_{\text{wp}} = 5.42\%$	$R_{\text{p}} = 4.01\%$	GOF = 2.56			
Ion	Wyckoff site	x	y	z	Occupancy	$B_{\text{eq}} (\text{\AA}^2)$
Ba	4e	0.497(6)	0.507(2)	0.256(9)	1	0.99(6)
Lu	2d	0.5	0	0	0.667	0.65(3)
Te	2c	0	0.5	0	1	0.65(2)
O1	4e	0.215(5)	0.251(4)	0.008(3)	1	0.85(5)
O2	4e	0.200(5)	0.771(6)	0.001(7)	1	0.90(5)
O3	4e	0.494(3)	0.016(6)	0.264(3)	1	0.82(5)

could not observe in XRD patterns of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) and hence rule out orthorhombic structure. However, in general for compounds crystallizing in  $P2_1/n$  symmetry, the value of  $\beta$  is larger than  $90^\circ$  if the size of at least one cation in the B-site is larger such as the rare earth ions in this case. These large cations can afford the distortions caused by the neighboring octahedral environment better than smaller cations with higher charges. Thus, it is plausible to conclude that the structure of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) double perovskites with a larger difference in ionic radii could be a distinct monoclinic unit cell rather than orthorhombic. To sum up, the monoclinic crystal structure derived from Raman and IR spectra is confirmed from the Rietveld refinement of the XRD patterns. The refined XRD patterns and parameters of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Tb, Dy, Ho, Er, Tm, Yb) are given in

Fig. S17–S23 and Table S24 (ESI<sup>†</sup>). Lattice parameters as well as unit cell volume are decreased along with lanthanide contraction of the rare earth ions.

In this system,  $\text{Ba}^{2+}$  and  $\text{O}^{2-}$  occupy the Wyckoff position 4e,  $\text{R}^{3+}$  and  $\text{Te}^{6+}$  occupy the Wyckoff positions 2d and 2c respectively. Occupancy is fixed at unity except for  $\text{R}^{3+}$  which has only 2/3rd occupancy of the atomic site. The satisfactory  $R$  factors,  $R_{\text{wp}}$ ,  $R_{\text{p}}$ ,  $R_{\text{exp}}$  and goodness of fit confirm the  $P2_1/n$  space group of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu). Selected bond distances of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$  are shown in Table 3 and bond distances of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Tb, Dy, Ho, Er, Tm, Yb) are shown in Table S25 (ESI<sup>†</sup>). The expected reduction of bond distances with lanthanide contraction of B-site cations, is an indication of the magnitude of distortion. The average Gd–O and Te–O bond lengths of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  are less than the previously reported Eu–O and Te–O bond lengths of  $\text{Ba}_2\text{Eu}_{2/3}\text{TeO}_6$ . Octahedra get tilted in order to accommodate the changes caused by the smaller ions and the average bond angle shifts from  $167^\circ$  for Gd–O–Te to  $170^\circ$  for Lu–O–Te from  $165^\circ$  for Eu–O–Te denotes minimization in distortion with lanthanide contraction of B-site cations.

#### Diffuse reflectance spectra of $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$ (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu)

The optical band gaps of all the synthesized compounds are determined using diffuse reflectance spectroscopy (DRS) in order to discover their potential to act as host materials for luminescence centers. The band gaps are determined using the

Table 3 Selected bond distances of  $\text{Ba}_2\text{Gd}_{2/3}\text{TeO}_6$  and  $\text{Ba}_2\text{Lu}_{2/3}\text{TeO}_6$

Bond	Bond length ( $\text{\AA}$ )	Bond	Bond length ( $\text{\AA}$ )
Gd–O1	2.272	Lu–O1	2.239
Gd–O2	2.248	Lu–O2	2.239
Gd–O3	2.249	Lu–O3	2.205
Te–O1	1.971	Te–O1	1.941
Te–O2	2.018	Te–O2	1.991
Te–O3	2.008	Te–O3	1.967



Kubelka–Munk method for direct band transition using the expression<sup>50</sup>

$$[F(R_{\infty})h\nu]^2 \propto (h\nu - E_g) \quad (2)$$

where  $F(R_{\infty})$  is the Kubelka–Munk function,  $h\nu$  is the energy in eV and  $E_g$  is the optical band gap. Similar to  $\text{Ba}_2\text{Ln}_{2/3}\text{TeO}_6$  (Ln = La, Pr, Nd, Sm and Eu), all the compounds exhibit a direct band transition. Fig. 6 shows the diffuse reflectance spectra (Kubelka–Munk method) of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu). The obtained band gaps are shown in the inset to Fig. 6 and the values remain almost constant. In  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu), the hybridization of  $\text{Ba}^{2+}$  5p,  $\text{R}^{3+}$  4f,  $\text{Te}^{6+}$  4d and  $\text{O}^{2-}$  2p states contribute to the formation of valence and conduction bands. In all these compounds, only the B-site cations, *i.e.* the rare earth ions, vary and their empty 4f orbitals are involved in bonding. In addition, the band gap energies ( $E_g$ ) of covalent solids are related to the electronegativity difference between the elements. Across a period, the electronegativity increases, which in turn increases the orbital overlap, resulting in larger band gaps, as in the case of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu).<sup>51</sup>

#### Photoluminescence spectra of $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:x\%\text{Eu}^{3+}$ ( $x = 2.5, 5, 7.5, 10, 12.5, 15, 17.5$ and $20$ )

In order to further analyze the optical properties of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu),  $\text{Eu}^{3+}$  ions are substituted in the B-site of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$  for eight different concentrations in accordance with the stoichiometry  $\text{Ba}_2\text{Y}_{2/3-x}\text{Eu}_x\text{TeO}_6$  ( $x = 0.025, 0.05, 0.075, 0.1, 0.125, 0.15, 0.175$  and  $0.2$ ). Their XRD patterns do not show the presence of any additional phases and the combined graph is shown in Fig. S26 (ESI†).  $\text{Eu}^{3+}$  ions are substituted at the B-site of the host lattice *i.e.*, the  $\text{Y}^{3+}$  site. The ionic radius of  $\text{Y}^{3+}$  in six coordination is  $0.9 \text{ \AA}$  and that of  $\text{Eu}^{3+}$  in six coordination is  $0.947 \text{ \AA}$ . This means  $\text{Eu}^{3+}$  ions replace  $\text{Y}^{3+}$  ions with smaller ionic radii and hence there is a possibility of unit cell expansion with  $\text{Eu}^{3+}$  concentration. The leftward shift of monoclinic 112 reflection around  $2\theta \approx 30^\circ$  indicates the enhancement in cell volume with the addition of  $\text{Eu}^{3+}$  ions. The

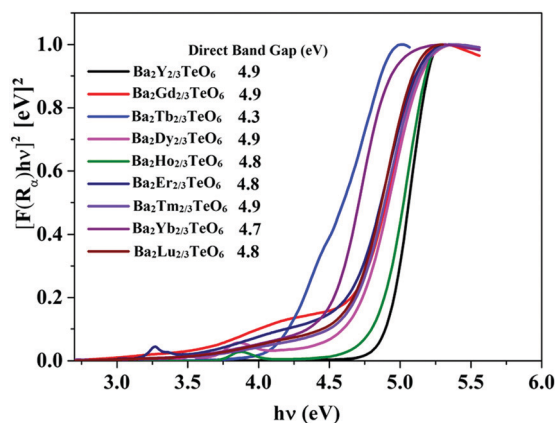


Fig. 6 DRS of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$  (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu). The inset shows the band gaps of  $\text{Ba}_2\text{R}_{2/3}\text{TeO}_6$ .

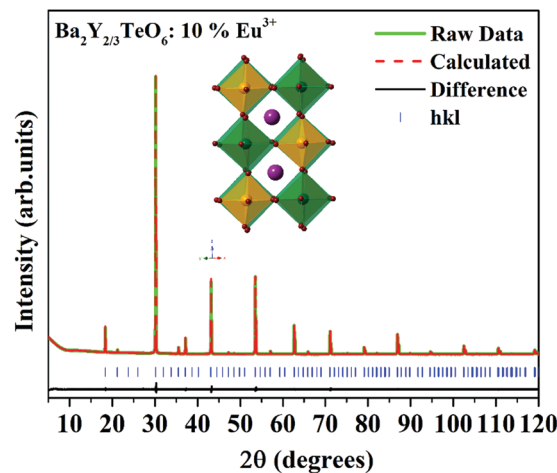


Fig. 7 The Rietveld refinement of the XRD pattern of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ . The inset shows the crystal structure of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$ .

shift in XRD peaks is depicted in Fig. S27 (ESI†) and a table of lattice parameters is shown in Table S28 (ESI†). Rietveld refinement of the XRD pattern of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  with optimal concentration fitted using the monoclinic ( $P2_1/n$ ) space group is shown in Fig. 7 and the refinement parameters are given in Table S29 (ESI†). In order to confirm the occupancy of activator ions in the  $\text{Y}^{3+}$  site and check the possibility of the crystallographic site swapping to the  $\text{Ba}^{2+}$  site,  $\text{Eu}^{3+}$  ions are distributed at different occupancies in both A- and B-sites in accordance with their stoichiometry, which results in poor refinement parameters. However, it is reported that such swapping cannot be detected directly from XRD at lower concentrations; only the Rietveld refinement of XRD patterns of higher concentrations will give a feasible result.<sup>52</sup> On the other hand, the relative intensity of electric and magnetic dipole transitions obtained from photoluminescence spectroscopy is a probe to detect any crystallographic off-centering of the  $\text{Eu}^{3+}$  ions.

The EDS of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  have an elemental composition of Ba, Te, O, and the rare earths Y and Eu. The elemental mapping shown in Fig. S30 (ESI†) exhibits a uniform distribution of elements in the phosphor. Table S8 (ESI†) gives the atomic percentage of elements obtained from EDS. DRS of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:x\%\text{Eu}^{3+}$  ( $x = 5, 10, 15$  mol%) and their Kubelka–Munk plots for finding the optical band gap are shown in Fig. S31(a) and (b) (ESI†). The reflectance spectra present absorption peaks at  $394 \text{ nm}$  and  $464 \text{ nm}$  corresponding to the characteristic f–f transitions of the  $\text{Eu}^{3+}$  ions. As the  $\text{Eu}^{3+}$  concentration increases, the band gap reduces from  $4.9 \text{ eV}$  of the host  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$  to  $4.3 \text{ eV}$  of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:15\%\text{Eu}^{3+}$  possibly due to the rise in density of the 4f band gap states within the forbidden band with  $\text{Eu}^{3+}$  content.

The band gap energy of  $4.9 \text{ eV}$  of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$  which corresponds to the wavelength of absorption in the UV region suggests the ability of this material to act as a host material for luminescent centres. Fig. 8a and b show the photoluminescence excitation (PLE) spectra of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  and the





emission spectra (PL) of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:x\% \text{Eu}^{3+}$  ( $x = 2.5, 5, 7.5, 10, 12.5, 15, 17.5$  and  $20$ ). The photoluminescence excitation spectrum monitored at  $592 \text{ nm}$  presents a broad band ranging from  $230$  to  $340 \text{ nm}$  attributed to the charge transfer states of  $\text{EuO}_6$  groups and the narrow peaks at  $362, 382, 394$  and  $464 \text{ nm}$  can be assigned to  ${}^7\text{F}_0\text{--}{}^5\text{D}_4, {}^7\text{F}_0\text{--}{}^5\text{G}_{2,3}, {}^7\text{F}_0\text{--}{}^5\text{L}_6$  and  ${}^7\text{F}_0\text{--}{}^5\text{D}_2$  transitions, respectively, which correspond to the characteristic f-f electronic transitions in the  $\text{Eu}^{3+}$  ions. The luminescence spectra present emissions at  $592$  ( ${}^5\text{D}_0\text{--}{}^7\text{F}_1$ ),  $610$  ( ${}^5\text{D}_0\text{--}{}^7\text{F}_2$ ),  $635$  ( ${}^5\text{D}_0\text{--}{}^7\text{F}_3$ ) and  $710$  ( ${}^5\text{D}_0\text{--}{}^7\text{F}_4$ ) nm in which the magnetic dipole transition ( ${}^5\text{D}_0\text{--}{}^7\text{F}_1$ ) is the most intense. The emission spectrum with high spectral resolution in the  $570\text{--}590 \text{ nm}$  spectral region is also shown in Fig. S32 (ESI<sup>†</sup>). The peak at  $582 \text{ nm}$  corresponds to the  ${}^5\text{D}_0\text{--}{}^7\text{F}_0$  transition of the  $\text{Eu}^{3+}$  ions. The energy level diagram of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  is shown in Fig. S33 (ESI<sup>†</sup>). When excited at  $276 \text{ nm}$ , ligand-to-metal charge transition occurs from the  $\text{O}^{2-}$  2p orbitals from the valence band to the empty 4f orbitals of  $\text{Eu}^{3+}$ . The absorbed energy is transferred to  $\text{Eu}^{3+}$  ions and the electrons from the highest energy levels relaxes non-radiatively to the  ${}^5\text{D}_0$  state. From there, electrons further transit to  ${}^7\text{F}_j$  ground levels giving visible emission. It can be seen that the photoluminescence emission intensity increases with  $\text{Eu}^{3+}$  ions concentration but decreases when  $\text{Eu}^{3+}$  concentration reaches  $12.5 \text{ mol}\%$ . As the doping concentration increases, the electric multipolar interactions between  $\text{Eu}^{3+}$  causes energy migration among them. This non-radiative energy transfer among the activator ions increases with doping concentration and correspondingly the emission intensity decreases. The critical distance ( $R_c$ ) of energy transfer among the activator ions can be determined using the equation:<sup>53</sup>

$$R_c = 2 \left[ \frac{3V}{4\pi x_c N} \right]^{1/3} \quad (3)$$

where  $V$  is the volume of the unit cell,  $x_c$  is the concentration of the activator ions beyond which quenching happens and  $N$  is the number of  $\text{Y}^{3+}$  ions in the unit cell. Substituting the values for  $V, N$  and  $x_c$  as  $295 \text{ \AA}^3, 6$  and  $0.1$  respectively, the critical distance is estimated to be  $9.79 \text{ \AA}$ . The value of  $R_c$  greater than  $4 \text{ \AA}$  implies electric multipolar interaction among the activator

ions. Based on Dexter's theory, if the interaction among the activator ions is multipolar, then it can be quantitatively explained using the equation<sup>54</sup>

$$\frac{I}{x} = k \left[ 1 + \beta(x)^{\theta} \right]^{-1} \quad (4)$$

where  $I$  is the luminescence intensity,  $x$  is the activator ion concentration after quenching,  $k$  and  $\beta$  are constants for the different types of interactions for the same system and  $\theta$  represents the type of interaction between the activator ions. The value of  $\theta = 3, 6, 8$  and  $10$  imply exchange interaction, electric dipole-dipole (D-D), electric dipole-quadrupole (D-Q) and electric quadrupole-quadrupole (Q-Q) interactions respectively.  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:x\% \text{Eu}^{3+}$  ( $x = 10, 12.5, 15, 17.5$  and  $20$ ) phosphors are selected and Fig. S34 (ESI<sup>†</sup>) represents the plots of  $\ln x$  vs.  $\ln(I/x)$  at different emissions of  $592, 610$  and  $635 \text{ nm}$ . The slopes of linear fittings of the plots are  $-\theta/3$  and they are  $-1.65$  ( $592 \text{ nm}$ ),  $-1.65$  ( $610 \text{ nm}$ ) and  $-1.51$  ( $635 \text{ nm}$ ). Hence  $\theta$  can be estimated to be  $4.95$  for  $592$  and  $610 \text{ nm}$  and  $4.53$  for  $635 \text{ nm}$ . The  $\theta$  values are close to  $6$  and thus the type of interaction among the activator ions is electric dipole-dipole in nature.

The relative intensity of the electric ( $610 \text{ nm}$ ) and magnetic ( $592 \text{ nm}$ ) dipole transition is a strong probe to determine the site symmetry of activator ions. Thus, hypersensitivity or the strong influence of the ligand field on the activator ions and hence on the emission intensity gives an idea about the site symmetry in which the ions remain. The dominant magnetic dipole transition in the PL spectra indicates that  $\text{Eu}^{3+}$  ions occupy a site with an inversion center or B-site. However, the emission at  $610 \text{ nm}$  denotes the occupancy of some of the  $\text{Eu}^{3+}$  ions in a non-center of symmetric environment or A-site of the lattice. Further, to investigate the photoluminescence properties of A-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$ , two different concentrations, a concentration lower than optimal concentration ( $5 \text{ mol}\%$ ) and optimal concentration ( $10 \text{ mol}\%$ ) for B-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$ , are substituted in the A-site of the lattice. The combined XRD patterns of A-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$  are shown in Fig. S35 (ESI<sup>†</sup>). The XRD patterns

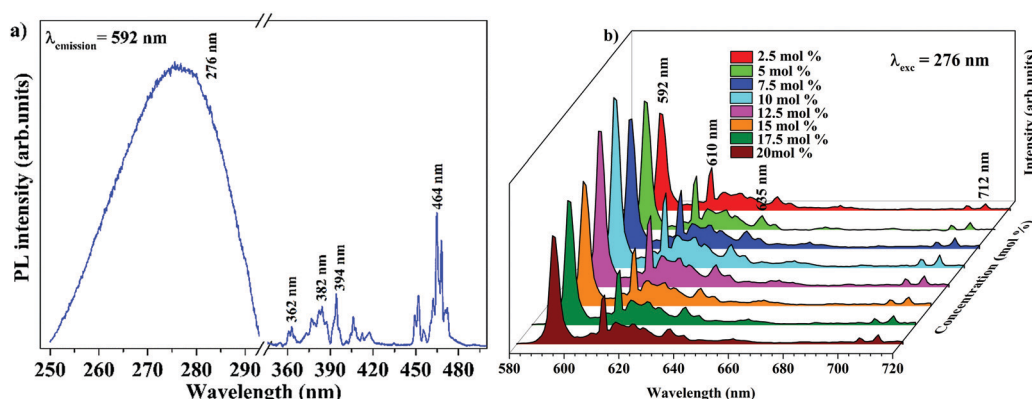


Fig. 8 (a) PLE of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  and (b) PL emission spectra of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:x\%\text{Eu}^{3+}$  ( $x = 2.5, 5, 7.5, 10, 12.5, 15, 17.5,$  and  $20$ ).



show an indistinct additional impurity phase around  $2\theta \approx 30^\circ$ . Interestingly the same luminescence spectrum is observed with more intense magnetic transitions as well as electric dipole transitions. The fluorescence intensity ratio between the electric ( ${}^5D_0-{}^7F_2$ ) and magnetic dipole ( ${}^5D_0-{}^7F_1$ ) transitions defined as the asymmetry ratio, is a measure of the distortion of  $\text{Eu}^{3+}$  ions from the symmetric environment of the host matrix. We expected a slightly larger asymmetry ratios for A-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$ , since in that case the probability of occurrence of electric dipole transitions is greater. Here the asymmetry ratio for  $\text{Ba}_{1.85}\text{Y}_{2/3}\text{Eu}_{0.1}\text{TeO}_6$ ,  $\text{Ba}_{1.925}\text{Y}_{2/3}\text{Eu}_{0.05}\text{TeO}_6$ ,  $\text{Ba}_2\text{Y}_{0.567}\text{Eu}_{0.1}\text{TeO}_6$  and  $\text{Ba}_2\text{Y}_{0.517}\text{Eu}_{0.05}\text{TeO}_6$  are obtained as 0.46, which implies  $\text{Eu}^{3+}$  ions prefer to occupy B-site rather than A-site even if the substitution is done on the A-site. This is in contradiction to the photoluminescence behavior of other double perovskites, which show a dominant electric dipole transition when the  $\text{Eu}^{3+}$  ions are substituted in an asymmetric site. Fig. 9 shows a comparison of PL spectra of A- and B-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$ . Raman spectra of A- and B-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  are shown in Fig. S36 (ESI<sup>†</sup>). The Raman spectrum does not exhibit any considerable changes in the low-energy lattice modes when  $\text{Eu}^{3+}$  is substituted in the A-site, which further confirms the above result.

### Temperature-dependent photoluminescence

Temperature-dependent photoluminescence spectra of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  in the range 80–500 K are shown in Fig. 10a. Below 300 K, the emission intensity almost maintains a steady value with no remarkable variation. However, above 300 K, the intensity of photoluminescence shows an appreciable change with rise in temperature. It is essential to probe the thermal stability of phosphors above room temperature, because temperature can influence the color stability and emission intensity, which is a major concern during fabrication of LEDs since they usually work above room temperature.

At 480 K, the maximum intensity reaches 41% of the emission intensity at room temperature. Thermal quenching is attained at

400 K and the effect can be better understood by determining the thermal activation energy. The thermal activation energy,  $\Delta E$  is determined from the Arrhenius equation

$$I_T = \frac{I_0}{1 + C \exp\left(\frac{-\Delta E}{kT}\right)} \quad (5)$$

where  $I_0$  is the original intensity,  $I_T$  is the intensity at a temperature  $T$ ,  $C$  is a constant,  $k$  is the Boltzmann constant ( $8.617 \times 10^{-5} \text{ eV K}^{-1}$ ) and  $\Delta E$  is the activation energy. A plot of  $1/kT$  vs.  $\ln(I_0/I_T - 1)$  is given in Fig. 10b and the activation energy,  $\Delta E$  is obtained as 0.15 eV. The exact mechanism of thermal quenching is given in Fig. S37 (ESI<sup>†</sup>). Thermal activation energy is defined as the energy required by the electrons to cross the  ${}^5D_0$  excited state to the Eu–O CTS and a larger value of  $\Delta E$  indicates good thermal stability of the phosphor. A lower activation energy indicates faster degradation of emission intensity of the phosphor. Generally, as temperature increases, phonon-assisted non-radiative transitions become significant and will suppress the luminescence intensity. However, in case of tellurate glasses, the phonon energy is very low, in the range of 800–900  $\text{cm}^{-1}$ , which suggests that  $\text{Eu}^{3+}$  in tellurate host materials are less affected by phonon-assisted non-radiative transitions.<sup>55</sup> Hence, we expect  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6$  activated with  $\text{Eu}^{3+}$  ions to exhibit exceptional photoluminescence behaviour and to be a potential candidate for solid-state lighting device applications. Even though its spectral characteristics are good enough for LED applications, unlike other tellurate phosphors, its thermal activation energy is slightly low. Thermal activation energies of various double perovskite tellurates are shown in Table 4.

### Temperature-dependent Raman spectra of $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$

In order to analyze the dependence of thermal quenching of  $\text{Eu}^{3+}$  ions on the structural changes in the host matrix, the temperature-dependent Raman spectra of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  are recorded in a temperature range of 93 K to 873 K. The spectral profile of the Raman spectra of phosphor show no evidence for phase transitions above or below room temperature. Fig. S38 (ESI<sup>†</sup>) shows the temperature-dependent Raman spectra of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ . The Raman bands around 730–820  $\text{cm}^{-1}$  above room temperature corresponding to the symmetric stretching vibrations of the B-site octahedral cations are shown in Fig. S39 (ESI<sup>†</sup>). The band near 770  $\text{cm}^{-1}$  at room temperature undergoes a red shift and broadens at elevated temperature, which implies that more vibrations occur even at low energies. The distortion of a B-site octahedra as well as tilting get enhanced at higher temperatures. Hence, distortions also affect the B-site  $\text{Eu}^{3+}$  ions, which further results in faster degradation of the  $\text{Eu}^{3+}$  emission due to the thermally stimulated non-radiative energy transfer from  $\text{Eu}^{3+}$  to the distortion defects.<sup>59</sup> In brief, the peak broadening and red shift above room temperature occur due to the temperature effects. The peak position as well as FWHM values are plotted in Fig. 11.



Fig. 9 A comparison of the PL spectra of A- and B-site substituted  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$ .



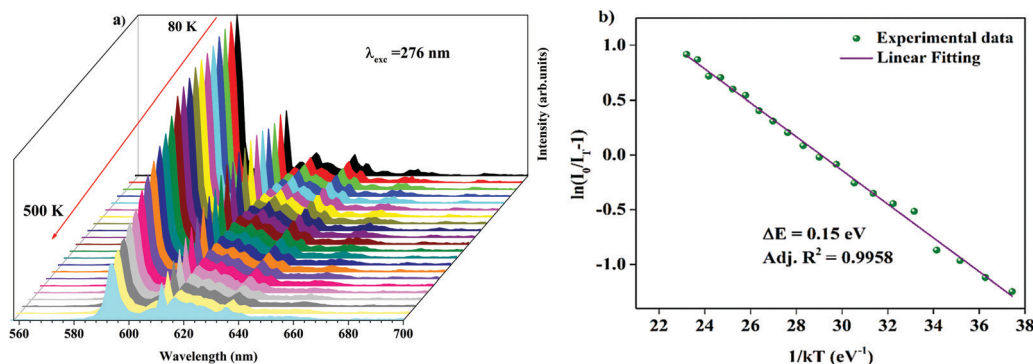


Fig. 10 (a) Temperature-dependent photoluminescence spectra of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ . (b) The Arrhenius plot of the temperature dependence in the range of 300–500 K of the PL emission intensity of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ .

Table 4 An overview of the activation energies and quantum yields of tellurate double perovskite phosphors and commercial red phosphors

Red phosphor	Activation energy (eV)	Quantum yield (%)	Ref.
$\text{Sr}_2\text{Si}_5\text{N}_8:\text{Eu}^{2+}$	0.42	80	56
$\text{Y}_2\text{O}_3:\text{Eu}^{3+}$	—	9.6	57
$\text{Y}_2\text{O}_2\text{S}:\text{Eu}^{3+}$	—	4.2	58
$\text{LiSrBiTeO}_6:\text{Eu}^{3+}$	0.29	—	28
$\text{Sr}_2\text{MgTeO}_6:\text{Eu}^{3+}$	0.27	—	29
$\text{NaMgGdTeO}_6:\text{Mn}^{4+}$	0.25	41.19	30
$\text{NaMgLaTeO}_6:\text{Mn}^{4+}$	0.25	57	31
$\text{NaLaCaTeO}_6:\text{Mn}^{4+}$	0.179	92.2	32
$\text{Sr}_2\text{MgTeO}_6:\text{Sm}^{3+}$	0.34	—	33
$\text{LiLaMgTeO}_6:\text{Mn}^{4+}$	0.46	—	34
$\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$	0.15	24	This work

### Temperature-dependent PL decay curves

The temperature-dependent PL lifetime decay curves in the range 80–500 K are obtained by exciting the phosphor  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  using 276 nm with  $\lambda_{\text{em}} = 592$  nm. Fig. 12a and b show the low-temperature and high-temperature behavior of the decay curves, respectively. The decay curves are well fitted using a double exponential function given by

$$I(t) = A_1 \exp(-t/\tau_1) + A_2 \exp(-t/\tau_2) + I_0 \quad (6)$$

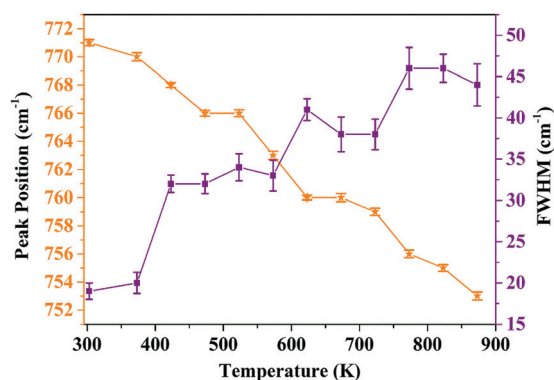


Fig. 11 Peak position and FWHM ( $\text{cm}^{-1}$ ) of the symmetric stretching vibrations of the B-site octahedron above room temperature (peak around  $770 \text{ cm}^{-1}$  at room temperature).

where  $I_0$  is the emission intensity at time  $t = 0$  ms and  $I(t)$  is the intensity at  $t = t$  ms.  $A_1$  and  $A_2$  are both constants, and  $\tau_1$  and  $\tau_2$  are the decay components. The average lifetimes at various temperatures can be determined using the fitting parameters obtained from eqn (6) and substituted in the following equation

$$\tau = \frac{A_1\tau_1^2 + A_2\tau_2^2}{A_1\tau_1 + A_2\tau_2} \quad (7)$$

The lifetime falls off from  $4.826 \pm 0.259$  ms at 80 K to  $2.906 \pm 0.139$  ms at 500 K due to the intensification of non-radiative relaxation rate with a rise in temperature, which in turn decreases the decay rate. Usually, the  $^5\text{D}_0$  measured lifetimes of  $\text{Eu}^{3+}$  are dominated by non-radiative relaxation mechanisms, such as multiphonon emission, direct or indirect phonon assisted energy transfer to the impurity traps or crossover to a low-lying ligand to the metal CT state.<sup>60</sup> Even though non-radiative relaxations are predominant at low temperatures, their effects become more evident at high temperatures in the form of a rapid decrease in lifetime. Fig. S 40 (ESI<sup>†</sup>) shows the decay curves of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:x\%\text{Eu}^{3+}$  ( $x = 5, 10, 12.5, 15$  and  $20$ ). Lifetimes are estimated as  $3.937 \pm 0.286, 3.784 \pm 0.218, 3.770 \pm 0.242, 3.511 \pm 0.170$  and  $2.935 \pm 0.066$  ms, respectively, for  $x = 5, 10, 12.5, 15$  and  $20$  mol%. The lifetime is found to decrease with concentration, due to the faster decay rates. The rate of increase of non-radiative transitions among the activator ions allows faster decay and hence a shortening of the lifetime. The room-temperature quantum yield of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  is 24%. The quantum yields of different tellurate red phosphors are shown in Table 4. Even though the quantum yield of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:\text{Eu}^{3+}$  is comparatively lower than that of other tellurates, it is much better than those of commercially available  $\text{Y}^{3+}$ -based red phosphors used in WLED applications, as shown in Table 4. Chromaticity coordinates obtained as (0.615, 0.384) imply that the phosphor exhibits an orange-red color, as shown in the inset of Fig. 12b. The chromaticity coordinates are close to those of commercial red phosphor  $\text{Sr}_2\text{Si}_5\text{N}_8:\text{Eu}^{2+}$  (0.62, 0.37). Correlated color temperature (CCT) is calculated using the McCamy method.<sup>61</sup>

$$\text{CCT} = -449n^3 + 3525n^2 - 6823.3n + 5520.33 \quad (8)$$



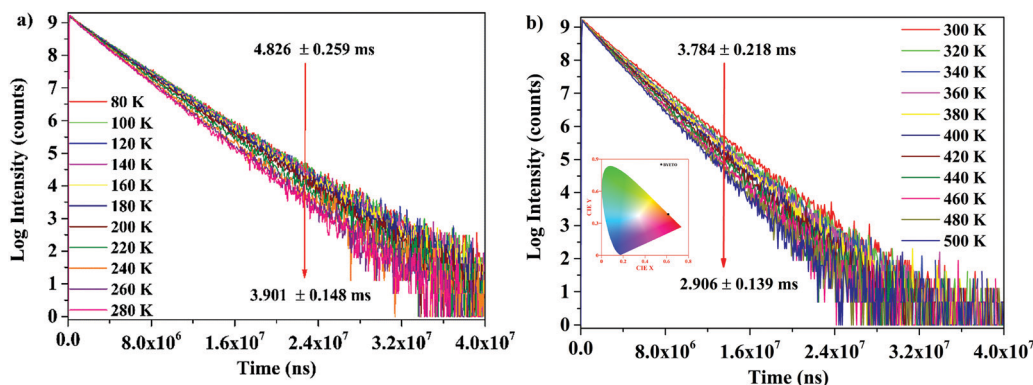


Fig. 12 (a) Low-temperature and (b) high-temperature decay profiles of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ . The inset shows the chromaticity diagram of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ .

where  $n = (x - x_e)/(y - y_e)$ .  $(x, y)$  are the chromaticity coordinates and  $(x_e, y_e)$  are (0.3320, 0.1858), the coordinates corresponding to the epicenter of convergence of the isotherm lines of the CIE 1931 chromaticity diagram. CCT is calculated as 1657 K, which indicates warmer yellow-red light.

### Optical thermometric properties of $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$

Optical thermometers using various phosphors explore certain parameters of luminescence like the fluorescence intensity ratio (FIR), lifetime, spectral bandwidth, *etc.* for calculating temperature sensitivity. The intensity ratio,  ${}^5\text{D}_0\text{-}^7\text{F}_1/{}^5\text{D}_0\text{-}^7\text{F}_2$ , and the emission lifetimes of  $\text{Eu}^{3+}$  ions in the temperature range 300–500 K are used to probe the sensitivity of the  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  phosphor. Hou *et al.*<sup>37</sup> proposed a new temperature-sensing formula for evaluating the FIR of  $\text{Eu}^{3+}$ -doped  $\text{Ba}_2\text{TiGe}_2\text{O}_8$ , which is equivalent to the general fluorescence intensity ratio formula  $\text{FIR} = B \times \exp(-\Delta E/k_B T)$ . The new FIR is the ratio of  ${}^5\text{D}_0\text{-}^7\text{F}_1$  and  ${}^5\text{D}_0\text{-}^7\text{F}_2$  transitions. A plot of temperature *vs.* FIR is shown in Fig. S41 (ESI<sup>†</sup>). The relative sensitivity is defined as

$$S_r = \frac{1}{\text{FIR}} \times \frac{\partial \text{FIR}}{\partial T} \quad (9)$$

The relative sensitivity of the  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$  phosphor is determined using the TeSen calculator, developed by

Kaczmarek *et al.*<sup>62</sup> for determining thermometric parameters in ratiometric optical thermometry. A plot of temperature *vs.* relative sensitivity obtained from FIR is given in Fig. 13a. The maximum relative sensor sensitivity is  $0.18\% \text{K}^{-1}$  at 300 K and it reduces to  $0.06\% \text{K}^{-1}$  at 500 K. The dependence of lifetime on temperature can be fitted using the Struck and Fonger model given by<sup>63</sup>

$$\tau(T) = \frac{1}{A + B \exp\left(\frac{-\Delta E}{kT}\right)} \quad (10)$$

where  $\tau(T)$  is the lifetime at temperature  $T$ ,  $A$  is a constant,  $B$  is the frequency factor,  $k$  is the Boltzmann constant and  $\Delta E$  is the thermal activation energy. Temperature *vs.* lifetime data was plotted and is shown in Fig. S42 (ESI<sup>†</sup>). The relative sensitivity,  $S_r$  is therefore given by

$$S_r = \frac{1}{\tau} \times \frac{\partial \tau}{\partial T} \quad (11)$$

A plot of temperature *vs.* relative sensitivity obtained from lifetime is given in Fig. 13b. The maximum sensitivity is  $0.136\% \text{K}^{-1}$  at 500 K and it reduces to  $0.100\% \text{K}^{-1}$  at 300 K. From a comparison of both results, the temperature sensor sensitivity for FIR is better than the lifetime measurement. A comparison of relative sensitivities of different phosphors

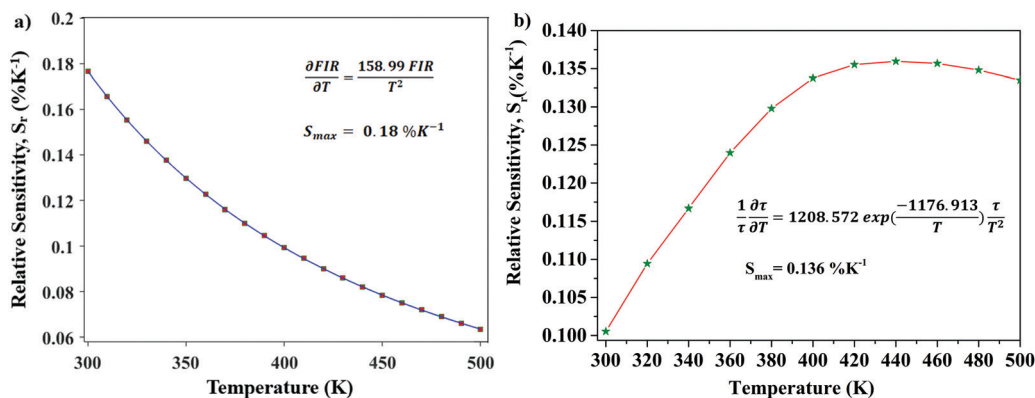


Fig. 13 (a) A plot of temperature *vs.* relative sensitivity obtained from FIR, and (b) a plot of lifetime *vs.* relative sensitivity of  $\text{Ba}_2\text{Y}_{2/3}\text{TeO}_6:10\%\text{Eu}^{3+}$ .



**Table 5** A comparison of the sensitivity values of various double perovskite phosphors

Phosphor	Temperature range (K)	Relative sensitivity ( $S_r$ ) % K <sup>-1</sup>
Ba <sub>2</sub> Y <sub>2/3</sub> TeO <sub>6</sub> :Eu <sup>3+</sup>	303–483	0.18 [present work]
Ba <sub>2</sub> La <sub>2/3</sub> TeO <sub>6</sub> :Eu <sup>3+</sup>	315–483	0.21 <sup>15</sup>
Gd <sub>2</sub> ZnTiO <sub>6</sub> :Pr <sup>3+</sup>	293–433	1.67 <sup>45</sup>
Y <sub>2</sub> MgTiO <sub>6</sub> :Mn <sup>4+</sup>	10–513	0.14 <sup>46</sup>
LiLaMgWO <sub>6</sub> :Er <sup>3+</sup>	303–483	2.24 <sup>47</sup>

is tabulated in Table 5 and the relative sensitivity of Ba<sub>2</sub>Y<sub>2/3</sub>TeO<sub>6</sub>:10% Eu<sup>3+</sup> indicates the ability of this phosphor to be used for temperature-sensing applications in the range 300–500 K. Thus, Ba<sub>2</sub>Y<sub>2/3</sub>TeO<sub>6</sub>:Eu<sup>3+</sup> phosphor can be used in non-contact optical thermometers.

### Judd–Ofelt analysis

Further analysis of the site symmetry modifications of Eu<sup>3+</sup> ions are investigated by determining the Judd–Ofelt intensity parameters  $\Omega_\lambda$  ( $\lambda = 2, 4$ ).<sup>64–69</sup> The  $\Omega_2$  parameter is an indicator of site asymmetry, whereas the  $\Omega_4$  parameter is sensitive to macroscopic properties, such as rigidity of the host materials, viscosity and dielectric constant. In this work, the intensity parameters were calculated from the emission spectrum, taking the <sup>5</sup>D<sub>0</sub>–<sup>7</sup>F<sub>1</sub> transition as the reference. The Judd–Ofelt intensity parameters and radiative parameters are presented in Table 6. The low value of the J–O parameter  $\Omega_2$  suggests that most of the Eu<sup>3+</sup> ions occupy a site with inversion symmetry, which is in good agreement with the PL spectrum. In addition, the <sup>5</sup>D<sub>0</sub>–<sup>7</sup>F<sub>1</sub> transition contributes almost 71% of the total radiative transition. The phosphor has a maximum internal quantum efficiency of 42.86%, which suggests the potential application of these phosphors in various technological applications, including WLEDs and optical thermometers. A detailed explanation of the Judd–Ofelt analysis is given in the ESI.†

## Conclusions

In summary, Ba<sub>2</sub>R<sub>2/3</sub>TeO<sub>6</sub> (R = Y, Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) were synthesized *via* a solid-state ceramic route, and their crystal structures and optical properties were investigated for

**Table 6** Judd–Ofelt intensity parameters and radiative parameters obtained from the emission spectrum and lifetime data

Judd–Ofelt intensity parameters	
$\Omega_2$ ( $\times 10^{-20}$ cm <sup>2</sup> )	0.26 $\pm$ 10 <sup>-4</sup>
$\Omega_4$ ( $\times 10^{-20}$ cm <sup>2</sup> )	0.04 $\pm$ 10 <sup>-4</sup>
Radiative parameters	
Radiative transition rate, $A_R$ (s <sup>-1</sup> )	113.28 $\pm$ 6.52
Non-radiative transition rate, $A_{NR}$ (s <sup>-1</sup> )	150.98 $\pm$ 8.69
Total transition rate, $A_T$ (s <sup>-1</sup> )	264.27 $\pm$ 15.22
Measured lifetime, $\tau_{obs}$ (ms)	3.784 $\pm$ 0.218
Calculated radiative lifetime, $\tau_{rad}$ (ms)	8.82 $\pm$ 0.51
Quantum efficiency, $\eta$ (%)	42.86 $\pm$ 0.72
Branching ratio of <sup>5</sup> D <sub>0</sub> – <sup>7</sup> F <sub>1</sub> transition, $\beta_{01}$ (%)	71.58 $\pm$ 4.89
Branching ratio of <sup>5</sup> D <sub>0</sub> – <sup>7</sup> F <sub>2</sub> transition, $\beta_{02}$ (%)	17.38 $\pm$ 4.89
Branching ratio of <sup>5</sup> D <sub>0</sub> – <sup>7</sup> F <sub>4</sub> transition, $\beta_{04}$ (%)	11.03 $\pm$ 4.89

the first time. Even though we expected a structural transition from monoclinic to cubic when the B-site ions varied from Gd<sup>3+</sup> to Lu<sup>3+</sup>, Raman and IR spectra presented more than four modes which contradicts our assumption. The Raman spectra were deconvoluted using the Lorentzian function and the space group was identified as *P2<sub>1</sub>/n*, which was further confirmed by the Rietveld refinement of the XRD patterns. The optical band gaps suggested that the compounds can act as host materials for luminescence centers, and their photoluminescence properties were broadly investigated *via* substituting Eu<sup>3+</sup> in the B-site of Ba<sub>2</sub>Y<sub>2/3</sub>TeO<sub>6</sub>. The luminescence spectra implied the presence of Eu<sup>3+</sup> ions at both A- and B-sites but they were mostly present at the B-sites. Eu<sup>3+</sup> ions substituted at the A-site of Ba<sub>2</sub>Y<sub>2/3</sub>TeO<sub>6</sub> exhibited similar PL spectra with an asymmetry ratio almost equal to that of B-site-substituted Ba<sub>2</sub>Y<sub>2/3</sub>TeO<sub>6</sub>. The thermal activation energy and the color parameters indicated the potential application of the phosphor in the field of solid-state lighting. Temperature-dependent Raman spectra of the phosphor with an optimal concentration suggested the dependence of structural distortions at elevated temperatures on thermal quenching. The lifetime decreases from 4.826  $\pm$  0.259 ms at 80 K to 2.906  $\pm$  0.139 ms at 500 K due to the intensification of non-radiative relaxation rate with a rise in temperature. Additionally, the phosphor shows a relative temperature sensitivity of 0.18% K<sup>-1</sup> at 300 K for FIR measurements, which is better than for lifetime measurements, and hence it could also find applications in ratiometric optical temperature sensing. The PL spectrum and J–O parameters together suggest the occupation of symmetric B-sites by the majority of Eu<sup>3+</sup> ions in the host lattice. In brief, Ba<sub>2</sub>Y<sub>2/3</sub>TeO<sub>6</sub>:Eu<sup>3+</sup> is the first double perovskite phosphor with defects that shows distinct photoluminescence behavior as well as temperature-sensing potential. The substitution of Eu<sup>3+</sup> ions as well other rare-earth ions into Ba<sub>2</sub>R<sub>2/3</sub>TeO<sub>6</sub> (R = Gd, Tb, Dy, Ho, Er, Tm, Yb, Lu) double perovskites might provide better photoluminescence properties.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

SCL is grateful for a DST-INSPIRE fellowship. The authors acknowledge DST SERB for financial support (YSS/000868/2014). The authors also acknowledge CLIF, University of Kerala, and Department of Optoelectronics, University of Kerala, for their experimental support.

## References

- 1 S. Vasala and M. Karppinen, *Prog. Solid State Chem.*, 2015, **43**, 1–36.
- 2 C. Moure and O. Pena, *Prog. Solid State Chem.*, 2015, **43**, 123–148.



- 3 M. T. Anderson, K. B. Greenwood, G. A. Taylor and K. R. Poeppelmeier, *Prog. Solid State Chem.*, 1993, **22**, 197–233.
- 4 M. C. Knapp and P. M. Woodward, *J. Solid State Chem.*, 2006, **179**, 1076–1085.
- 5 J.-H. Park and P. M. Woodward, *Int. J. Inorg. Mater.*, 2000, **2**, 153–166.
- 6 A. Dias, G. Subodh, M. T. Sebastian, M. M. Lage and R. L. Moreira, *Chem. Mater.*, 2008, **20**, 4347–4355.
- 7 N. Panda, B. N. Parida, R. Padhee and R. N. P. Choudhary, *J. Electron. Mater.*, 2015, **44**, 4275–4282.
- 8 E. S. Madruga, Y. Sun, A. M. Arevalo-Lopez and J. P. Attfield, *Chem. Commun.*, 2019, **55**, 2605–2608.
- 9 R. Yu, A. Fan, T. Li, M. Yuan and J. Wang, *Mater. Chem. Phys.*, 2017, **196**, 75–81.
- 10 K. N. Nandha and A. Nag, *Chem. Commun.*, 2018, **54**, 5205–5208.
- 11 R. J. Cava, B. Batlogg, J. J. Krajewski, R. Farrow, L. W. Rupp, A. E. White, K. Short, W. F. Peck and T. Kometani, *Nature*, 1988, **332**, 814–816.
- 12 J. Su, Z. Yang, X. Lu, J. Zhang, L. Gu, C. Lu, Q. Li, J. Liu and J. Zhu, *ACS Appl. Mater. Interfaces*, 2015, **7**, 13260–13265.
- 13 C. Artinini, *J. Eur. Ceram. Soc.*, 2016, **37**, 1–14.
- 14 T. Kong and R. J. Cava, *Mater. Res. Express*, 2017, **4**, 106101.
- 15 S. C. Lal, V. Lalan and G. Subodh, *Inorg. Chem.*, 2018, **57**, 6226–6236.
- 16 C. Feldmann, T. Jüstel, C. R. Ronda and P. J. Schmidt, *Adv. Funct. Mater.*, 2003, **13**, 511–516.
- 17 M. Shang, C. Li and J. Lin, *Chem. Soc. Rev.*, 2014, **43**, 1372–1386.
- 18 J. Meyer and F. Tappe, *Adv. Opt. Mater.*, 2015, **3**, 424–430.
- 19 P. Pust, P. J. Schmidt and W. Schnick, *Nat. Mater.*, 2015, **14**, 454–458.
- 20 S. Li, X. Wei, K. Deng, X. Tian, Y. Qin, Y. Chen and M. Yin, *Curr. Appl. Phys.*, 2013, **13**, 1288–1291.
- 21 L. Li, W. Chang, W. Chen, Z. Feng, C. Zhao, P. Jiang, Y. Wang, X. Zhou and A. Suchocki, *Ceram. Int.*, 2017, **43**, 2720–2729.
- 22 S. Wang, Q. Sun, B. Devakumar, J. Liang, L. Sun and X. Huang, *J. Alloys Compd.*, 2019, **804**, 93–99.
- 23 Q. Sun, S. Wang, B. Devakumar, L. Sun, J. Liang, T. Sakthivel, S. J. Dhoble and X. Huang, *J. Alloys Compd.*, 2019, **804**, 230–236.
- 24 Z. Zhang, L. Sun, B. Devakumar, G. Annadurai, J. Liang, S. Wang, Q. Sun and X. Huang, *J. Lumin.*, 2020, **222**, 117173.
- 25 X. Huang, Q. Sun and B. Devakumar, *J. Lumin.*, 2020, **225**, 117373.
- 26 J. Liang, B. Devakumar, L. Sun, G. Annadurai, S. Wang, Q. Sun and X. Huang, *J. Lumin.*, 2019, **214**, 116605.
- 27 Z. Zhang, L. Sun, B. Devakumar, J. Liang, S. Wang, Q. Sun, S. J. Dhoble and X. Huang, *J. Lumin.*, 2020, **221**, 117105.
- 28 J. He, Z. Gao, S. Liu, J. H. Jeong, R. Yu and B. Deng, *J. Lumin.*, 2018, **202**, 7–12.
- 29 J. Liang, S. Zhao, X. Yuan and Z. Li, *Opt. Laser Technol.*, 2018, **101**, 451–456.
- 30 K. Li, H. Lian and R. V. Deun, *J. Lumin.*, 2018, **198**, 155–162.
- 31 K. Li, H. Lian, R. V. Deun and M. G. Brik, *Dyes Pigm.*, 2019, **162**, 214–221.
- 32 K. Li and R. V. Deun, *Chem. Commun.*, 2019, **55**, 10697–10700.
- 33 L. Zhao, P. Xu, F. Fan, J. Yu, Y. Shang, Y. Li, L. Huang and R. Yu, *J. Lumin.*, 2019, **207**, 520–525.
- 34 L. Li, G. Tian, W. Chang, Y. Yan, F. Ling, S. Jiang, G. Xiang and X. Zhou, *J. Alloys Compd.*, 2020, **832**, 154905.
- 35 Y. Ren, R. Cao, T. Chen, L. Su, X. Cheng, T. Chen, S. Guo and X. Yu, *J. Lumin.*, 2019, **209**, 1–7.
- 36 X. Wang, Q. Liu, Y. Bu, C.-S. Liu, T. Liu and X. Yan, *RSC Adv.*, 2015, **5**, 86219–86236.
- 37 B. Hou, M. Jia, P. Li, G. Liu, Z. Sun and Z. Fu, *Inorg. Chem.*, 2019, **58**, 7939–7946.
- 38 S. C. Lal, A. Rajan and G. Subodh, *Mater. Today: Proc.*, 2017, **4**, 4396–4402.
- 39 R. Yu, C. Wang, J. Chen, Y. Wu, H. Li and H. Ma, *ECS J. Solid State Sci. Technol.*, 2014, **3**, 33–37.
- 40 D. Gu, K. Du, L. Qin and H. J. Seo, *Mater. Lett.*, 2016, **177**, 64–67.
- 41 Y. Yang, L. Wang, P. Huang, Q. Shi, Y. Tian and C. Cui, *Polyhedron*, 2014, **129**, 65–70.
- 42 W. Xie, Y. W. Mo, C. W. Zou, F. W. Kang and G. H. Sun, *Inorg. Chem. Front.*, 2018, **5**, 1076–1084.
- 43 J. Luo, M. Hu, G. Niu and J. Tang, *ACS Appl. Mater. Interfaces*, 2019, **11**, 31575–31584.
- 44 G. Zhou, X. Jiang, J. Zhao, M. S. Molokeev, Z. Lin, Q. Liu and Z. Xia, *ACS Appl. Mater. Interfaces*, 2018, **10**, 24648–24655.
- 45 Y. Gao, Y. Cheng, T. Hu, Z. Ji, H. Lin, J. Xu and Y. Wang, *J. Mater. Chem. C*, 2018, **6**, 11178–11183.
- 46 P. Cai, L. Qin, C. Chen, J. Wang, S. Bi, S.-I. Kim, Y. Huang and H. J. Seo, *Inorg. Chem.*, 2018, **57**, 3073–3081.
- 47 W. Ran, H. M. Noh, S. H. Park, B. R. Lu, J. H. Kim, J. H. Jeong, J. Shi and G. Liu, *RSC Adv.*, 2019, **9**, 7189–7195.
- 48 A. K. Azad, S. Ivanov, S. G. Eriksson, H. Rundlof, J. Eriksen, R. Mathieu and P. Svedlindh, *J. Magn. Magn. Mater.*, 2001, **237**, 124–134.
- 49 A. K. Azad, S. G. Eriksson, S. A. Ivanov, R. Mathieu, P. Svedlindh, J. Eriksen and H. Rundlof, *J. Alloys Compd.*, 2004, **364**, 77–82.
- 50 A. E. Morales, E. S. Mora and U. Pal, *Rev. Mex. Fis. S*, 2007, **53**, 18–22.
- 51 P. A. Cox, *Instant notes in Inorganic Chemistry*, Taylor & Francis, London, 2nd edn, 2004, ch. D7, pp. 125–126.
- 52 R. Phatak, S. K. Gupta, K. Krishnan, S. K. Sali, S. V. Godbole and A. Das, *Dalton Trans.*, 2014, **43**, 3306–3312.
- 53 G. Blasse, *Philips Res. Rep.*, 1969, **24**, 131–144.
- 54 L. G. Van Uitert and L. F. Johnson, *J. Chem. Phys.*, 1966, **44**, 3514–3522.
- 55 H. Cankaya and A. Sennaroglu, *Appl. Phys. B: Lasers Opt.*, 2010, **99**, 121–125.
- 56 R.-J. Xie, N. Hirotsaki, T. Suehiro, F.-F. Xu and M. Mitomo, *Chem. Mater.*, 2006, **18**, 5578–5583.
- 57 S. Som, S. Das, S. Dutta, H. G. Visser, M. K. Pandey, P. Kumar, R. K. Dubey and S. K. Sharma, *RSC Adv.*, 2015, **5**, 70887–70898.
- 58 S. Som, P. Mitra, V. Kumar, V. Kumar, J. Terblans, H. C. Swart and S. K. Sharma, *Dalton Trans.*, 2014, **43**, 9860–9871.



- 59 C. Wang, S. Ye and Q. Zhang, *Opt. Mater.*, 2015, **75**, 337–346.
- 60 M. T. Berry, P. S. May and H. Xu, *J. Phys. Chem.*, 1996, **100**, 9216–9222.
- 61 C. S. McCamy, *Color Res. Appl.*, 1991, **17**, 142–144.
- 62 A. M. Kaczmarek, R. V. Deun and M. K. Kaczmarek, *Sens. Actuators, B*, 2018, **273**, 696–702.
- 63 J. Zhou, R. Lei, H. Wang, Y. Hua, D. Li, Q. Yang, D. Deng and S. Xu, *Nanophotonics*, 2019, **8**, 2347–2358.
- 64 W. F. Krupke, *Phys. Rev.*, 1966, **145**, 325–337.
- 65 B. R. Judd, *Phys. Rev.*, 1962, **127**, 750–761.
- 66 G. S. Ofelt, *J. Chem. Phys.*, 1962, **37**, 511–520.
- 67 M. P. Hehlen, M. G. Brik and K. W. Kramer, *J. Lumin.*, 2013, **136**, 221–239.
- 68 B. M. Walsh, *Advances in Spectroscopy for Lasers and Sensing conference proceedings*, 2005, ch. 21, pp. 403–433.
- 69 J. D. L. Dutra, T. D. Bispo and R. O. Freire, *J. Comput. Chem.*, 2014, **35**, 772–775.

