



Cite this: *Mater. Horiz.*, 2023, 10, 5538

Received 8th August 2023,
Accepted 5th October 2023

DOI: 10.1039/d3mh01262j

rsc.li/materials-horizons

A spectroscopic assessment of static and dynamic disorder in a film of a polythiophene with a planarized backbone†

Konstantin Schötz,^a Fabian Panzer,^{id} ^a Michael Sommer,^{id} ^b Heinz Bässler^c and Anna Köhler^{id} *^{ac}

The optoelectronic performance of organic semiconductor devices is related to the static and dynamic disorder in the film. The disorder can be assessed by considering the linewidth of its optical spectra. We focus on identifying the effect of conjugation length distribution on the static energetic disorder. Hence, we disentangle the contributions of static and dynamic disorder to the absorption and emission spectra of poly(3-(2,5-dioctylphenyl)-thiophene) (PDOPT) by exploring how the linewidth and energy of the spectra evolve upon cooling the sample from 300 K to 5 K. PDOPT has sterically hindered side chains that arrange such as to cause a planarized polymer backbone. This makes it a suitable model for a quasi-one-dimensional molecular system. By modelling the conjugated segments as coupled oscillators we find that the linewidth contribution resulting from the variation of conjugation length decreases linearly with decreasing exciton energy and extrapolates to zero at the energy corresponding to an infinite chain. These results provide a new avenue to the design of low disorder and hence high mobility polymeric semiconductors.

New concepts

The charge carrier mobility of organic semiconductors, and hence the performance of optoelectronic devices, relates to the energetic disorder that prevails in the material, with low disorder usually resulting in high mobility values. This article illustrates how one can disentangle the signatures of static and dynamic disorder in optical spectra such as to identify their contributions and structural origin in a material. For low-molecule weight molecules, the static disorder is largely determined by the dispersion forces with neighbouring molecules. For polymers, there is an additional contribution that results from the distribution of conjugation length. By analysing the linewidth of the optical spectra we show that the overall static disorder reduces with increasing conjugation length and vanishes in the infinite chain limit. The reason for this is two-fold. First, there is an energy variation along the polymer chain that arises from dispersion interactions with adjacent sites. Our results suggest that these energies average out with increasing length of the conjugated system, akin to the effects of motional narrowing. Second, the transition energies of excited states in polymers are well known to show a parabola-like dependence on the inverse conjugation length. We show that this implies a vanishing energy variation for long conjugation lengths. Our results imply that the design of conjugated polymers with very high conjugation length, typically achieved by backbone planarization, may provide a route towards high mobility polymeric compounds.

1. Introduction

In an array of small molecules the absorption and fluorescence (PL) spectra are broadened due to dynamic and static disorder (Fig. 1). Static disorder reflects the distribution of dispersion forces such as van-der-Waals interactions within the random environment of the chromophore. Dynamic disorder, in contrast, is caused by the time-dependent coupling between the

^a Soft Matter Optoelectronics and Bavarian Polymer Institute (BPI), University of Bayreuth, Universitätsstr. 30, 95447 Bayreuth, Germany

^b Institute for Chemistry, Chemnitz University of Technology, Straße der Nationen 62, 09111 Chemnitz, Germany

^c Bayreuth Institute of Macromolecular Research (BIMF), University of Bayreuth, Universitätsstr. 30, 95447 Bayreuth, Germany.

E-mail: anna.koehler@uni-bayreuth.de

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3mh01262j>



Anna Köhler

I always enjoyed reading the stimulating articles in Materials Horizons, and I like its focus on conceptual advances, as well as the breadth of the science covered by it. Of course, I was always delighted when I was able to contribute myself a few times. I very much appreciate the journal being published by the Royal Society of Chemistry, as an organization that aims to represent and serve the scientific community in many different ways. The 10th anniversary is a very good moment to celebrate this, and to look out for the next decade of exciting research. Congratulations!



Temperature-dependent optical spectroscopy and Raman spectroscopy

Temperature-dependent PL and absorption spectra were measured in a home-built setup. The setup consists of an electrically heatable continuous flow cryostat (Oxford Instruments), controlled by a temperature controller (Oxford Instruments ITC503S). A tungsten lamp (LOT-Oriel) serves as a white light source for the absorption measurements. For PL measurements, the sample is excited with a diode laser (Coherent COMPASS 405-50 CW) emitting at 405 nm. The light (PL or transmitted white light) is focused into a spectrograph (Andor Shamrock SR303i) and it is detected with a silicon CCD-camera (Andor iDus DU420a-OE). The optical density is calculated from the measured transmitted white light with the help of a reference measurement of an empty substrate. The recorded PL is corrected for self-absorption effects and for the detection efficiency of the setup.

The Raman spectrum of the PDOPT thin film was recorded using a commercial confocal Raman microscope (WITec alpha300

RA+) coupled to a spectrometer (UHTS 400S NIR) and a CCD camera (Andor iDUS DU401 BR-DD). The excitation wavelength was 785 nm. The recorded spectrum was background corrected.

3. Results

The normalized temperature-dependent PL and absorption spectra are shown in Fig. 2(a) and (b), respectively (see Fig. S1, ESI† for unnormalized data). At 300 K, the spectra agree well with reported spectra of highly aligned crystalline PDOPT samples.^{10,33,34} The PL shows already a clear vibronic progression, with the 0–0-peak being at 2.05 eV and vibronic peaks visible at 1.89 eV, 1.71 eV and 1.54 eV. Upon cooling, the spectrum shifts to lower energies, with the 0–0-peak reaching 2.008 eV at 5 K, and the linewidth reduces significantly. Thereby, additional vibronic features of energetically lower vibrational modes around 1.97 eV, 1.92 eV and 1.87 eV, and also between 1.68 eV and 1.80 eV become clearly visible.



Fig. 2 Normalized temperature dependent (a) PL and (b) absorption of the PDOPT thin film. The temperature difference between two adjacent lines is 20 K, except for the lowest temperature. Here, the difference is 15 K going from 20 K to 5 K. (c), (d) PL (solid) and absorption (dashed) of the PDOPT film at (c) 300 K and (d) 5 K. (e) chemical structure of PDOPT.



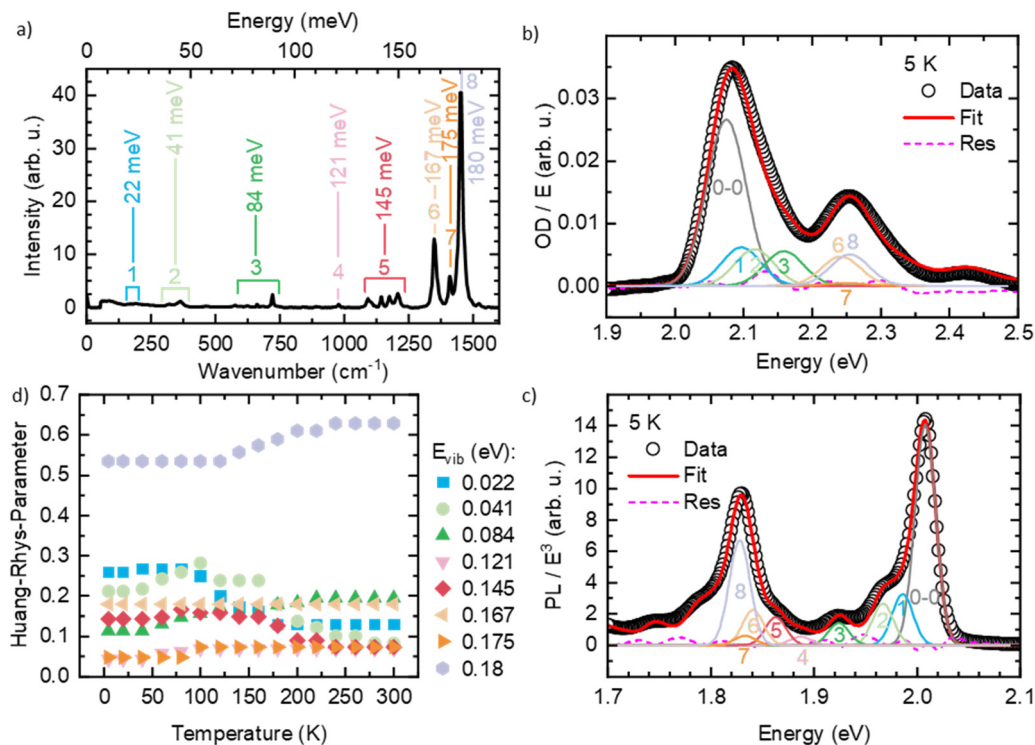


Fig. 3 (a) Raman-spectrum of the PDOPT thin film taken at room temperature. Also indicated are the (effective) vibrational modes used for the Franck-Condon-fits. (b), (c) Exemplary fits of a Franck-Condon-progression to (b) the PL and (c) the absorption at 5 K for the spectra of the interacting, aggregated chains. (d) Temperature-dependence of the Huang-Rhys parameters of the PL spectra.

excitation, singlet excitons are created that execute a random walk among the density of state (DOS) distribution. This gives rise to spectral diffusion of the excitons towards tail state of the DOS distribution. The fluorescence (PL) spectrum is therefore off-set from the absorption spectrum by the amount of spectral relaxation combined with temperature dependent spectral broadening. The theory of random walks predicts that under the condition of low intensity the excitons should relax to quasi-equilibrium at an energy of σ^2/kT below the center of the DOS distribution unless the jump rate of the exciton becomes less than the rate of its intrinsic decay. Usually this occurs when the exciton has relaxed by an amount of $2.5-3.0 \cdot \sigma$.^{19,39} If the excitations reach thermal quasi-equilibrium, the width of the DOS distribution that is occupied in this relaxation process is maintained.⁴⁰ Otherwise, the distribution of occupied states narrows up to about 2/3 of the total DOS width.³⁰ Since the standard deviation of the absorption spectrum of the PDOPT film is about 35 meV one would expect (i) that the PL spectrum would first bear out a red-shift upon sample cooling but tend to saturate at a temperature of (150 ± 15) K and (ii) that the width of the PL-spectrum would amount to at least 23 meV.

Fig. 2 and 4 show that the PL spectrum shifts continuously down to roughly 20 K and its standard deviation reaches an unexpectedly low value of 10 meV. This is in striking disagreement with the conventional relaxation concept. Conjecturing that the temperature dependent red-shift of the PL emission and the line narrowing have a common origin, we plotted the variance σ^2 of the 0-0 feature of the PL spectrum against its

spectral position energy at a given temperature (Fig. 5). We find that σ^2 increases linearly with energy up to an energy of 2.03 eV. Above 2.03 eV, σ^2 maintains to increase linearly with E_{0-0} yet with a larger slope. We associate the change of slope with the change in the contribution of phonon modes that couple to the emission, *cf.* Fig. 3(d).

We argue that such a correlation is a consequence of the fact that PDOPT consists of long π -conjugated chromophores, where the energy of the singlet exciton depends on chromophore length. Based upon the coupled oscillator model of Lewis and Calvin,⁴¹ W. Kuhn – not to be confused with H. Kuhn who proposed the particle-in-a-box model – predicted that for moderate to long numbers n of double bonds in the conjugated system, the energy of the chromophores' excited state should scale as

$$E_n = E_{n,\infty} - \beta \cdot \left(\frac{\pi}{n+1} \right)^2 \quad (4)$$

in which $E_{n,\infty}$ is the energy of the exciton of an infinitely long conjugated unit and β is the coupling energy.³¹

As a consequence of this parabolic dependence of E_n on the inverse length of the conjugated unit, any statistical variation of the conjugation length must contribute to the static disorder of the system. This applies not only if the physical length of the conjugated units differs, but also when the conjugation length is reduced by poor coupling, *e.g.* due to torsions, along the chromophore.^{41,42} Similarly, this statistical variation in energy should vanish when the conjugation length becomes infinite ($n \rightarrow \infty$). This is illustrated in Fig. 6.





Fig. 4 (a) Energetic position of the 0–0 peak (E_{0-0}) and (b) linewidth Sigma of the PL (black) and the absorption spectra (red) as a function of temperature, as extracted from the Franck–Condon-analysis. Dashed lines are guides to the eye, linearly extrapolating the values to 0 K. The blue asterisk in panel (b) indicates the average linewidth of the zero phonon line (ZPL) of isolated PDOPT chains from the work of Raithel *et al.*¹¹ (c) σ^2 as a function of temperature.

Using eqn (4) and the mean value theorem, it is straightforward to see that a variation in the inverse length ($1/n + 1$) of the conjugated segment translates into a corresponding variation on the excited state energy E_n according to

$$\frac{\partial E_n}{\partial(1/n + 1)} = 2\beta \frac{\pi}{n + 1} \quad (5)$$

Correspondingly, any statistical distribution in the inverse conjugation lengths results in a statistical distribution of excited states energies. Hence, the variance σ^2 should be proportional to $(1/n + 1)^2$, and thus by eqn (4) proportional to $E_n - E_{n,\infty}$, as is experimentally observed in Fig. 5.

The variance of the 0–0 feature of the PL spectrum is therefore the sum of three contributions, *i.e.* (1) of dynamic disorder, σ_{dyn}^2 , (2) the static disorder due to electrostatic dispersion interactions between the excited chain with the local dielectric environment (van-der-Waals coupling), σ_{vdW}^2 , and (3) the static disorder due to the variation of the conjugation length, σ_{CL}^2 .

Dynamic disorder is related to the interaction between an excited state and the local environment due to the electron–phonon-coupling that alters the site energy. The phonon modes involved are typically very low-energy modes, *e.g.* well below 10 meV. At sufficiently high temperatures at which low energy

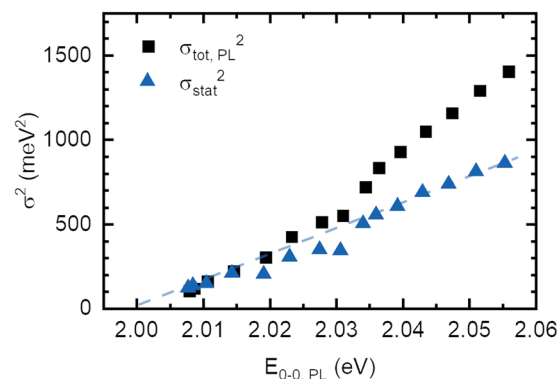


Fig. 5 Square of the PL linewidth as a function of E_{0-0} of the PL (black squares), as well as the difference between the square of the PL linewidth and the temperature-dependent part of the linewidth of the absorption spectra (blue triangles). The blue dashed line is a linear fit that serves as a guide to the eye.

vibrations can be treated classically, the variance σ_{dyn}^2 , is related to the electron–phonon coupling parameter λ via $\sigma_{\text{dyn}}^2 = 2\lambda kT$.¹ It is responsible for the temperature-dependent evolution of the spectral width of an excitation in a system in which static disorder is temperature-independent. This reasoning applies to the absorption spectrum of a PDOPT film. Fig. 4(a) and (b) shows that between 5 K and 300 K the absorption spectra bear out only weak blue-shift upon heating, accompanied by some broadening. This temperature-dependent change of the absorption spectrum must therefore solely be accounted for by temperature dependent line broadening due to dynamic disorder. The variance of the 0–0 feature of the absorption spectrum above 40 K indeed increases linearly with temperature as theoretically predicted (see Fig. 4(c) and Fig. S5, ESI[†]) and yields a λ of 30 meV for the temperature dependent dynamic disorder.

Making the approximation that the effect of dynamic disorder be the same in absorption and emission, we subtract the contribution of temperature-dependent dynamic disorder from the total variance of the PL spectrum (Fig. 5). As the excited state potential is, in general, more shallow than the ground state

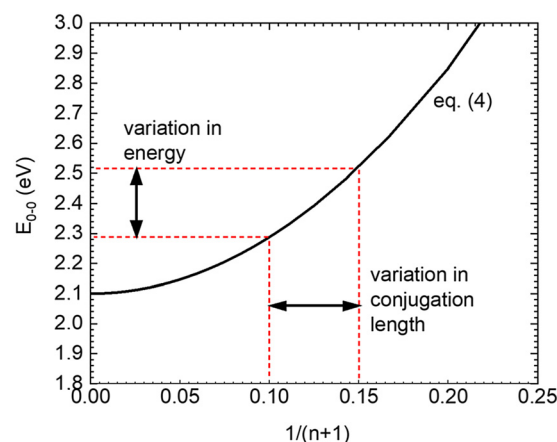


Fig. 6 Illustration on the relation between the variations of conjugation length and transition energy on the basis of eqn (4). n denotes the number of double bonds, E_{0-0} is the energy of the first excited singlet state. The values are parametrized to describe PDOPT.



potential, *i.e.* $\lambda_{\text{ES}} < \lambda_{\text{GS}}$, this approximation is subtracting too little, *i.e.* it gives an upper bound for the remaining quantity. The remaining quantity is the temperature-independent dynamic disorder and the static disorder. For PDOPT with its planarized backbone, coupling to phonon modes at 0 K is very weak, as evident from the lack of a significant phonon wing in the single molecule spectra.¹¹ Hence, the temperature-independent dynamic disorder is negligible in PDOPT, and the remaining quantity corresponds to an upper bound for the static disorder, *i.e.* $\sigma_{\text{CL}}^2 + \sigma_{\text{vdW}}^2$. This disorder contribution decreases linearly with decreasing energy of the 0–0 PL and extrapolates to zero at an excited state energy of (2.000 ± 0.003) eV (Fig. 5). We recall from the context of eqn (4) that the limit of vanishing statistical variance corresponds to the limit of infinite conjugation length. Within experimental accuracy, this value of (2.000 ± 0.003) eV this agrees with the energy for the excited state of PDOPT chain extrapolated to 0 K, *i.e.* where spectral diffusion would reach the longest conjugated segments. (Fig. 4(a)). This does not only verify the hypothesis that the narrowing of the 0–0 PL line is the signature of the parabolic shape of the exciton spectrum as a function of reciprocal conjugation length, but also indicates that the van-der-Waals contribution to static disorder (σ_{vdW}^2) decreases similarly with increases conjugation length. We interpret this as a signature of exchange narrowing that occurs when an excitation in π -bonded chain becomes more extended and the effect of the rough environment is progressively smeared out, akin to motional narrowing.^{7,43,44}

To relate the energy of the 0–0 feature of the PL spectrum of a PDOPT film to the conjugation length we resort on the work of Wasserberg *et al.*⁴⁵ who measured the PL spectra of 2–6 membered oligomers of thiophene. An analysis of her data in terms of eqn (4) yields $\beta = (-1.9 \pm 0.05)$ eV and $E_{n,\infty} = 2.10 \pm 0.05$ eV. The extrapolated value of the exciton energy of an infinite PDOPT chain, (2.000 ± 0.003) eV, is roughly by 0.10 eV below the extrapolated value of 2.10 ± 0.05 eV for an infinite thiophene chain, as illustrated in Fig. 6. Raithel *et al.* attributed this to a different charge transfer character a PDOPT relative to a thiophene chain.¹¹ That difference between the $E_{n,\infty}$ value may, however, simply be the result of the increased solvent shift of the S_1 – S_0 transition of PDOPT due to the polarizable side groups. Alternatively, the lower $E_{n,\infty}$ value may result from the weak, predominantly J-type, coupling that prevails between the planarized chromophores here, analogous to that observed in planarized MEH-PPV.⁴⁶ We recall that we are investigating those chains in the film that form aggregates, and that fitting these aggregates with eqn (1) yields a value of $\alpha \approx 1.1$, indicative of weak, predominant J-type, coupling.^{47,48}

Adopting the same β -value for a poly-thiophene chain and a PDOPT chain may be questionable yet is supported by a comparison between present data and those of Raithel *et al.* These authors observed that the zero-phonon-line (ZPL) transition of a 16 membered PDOPT oligomer embedded in a decane-matrix is at an energy of 2.11 eV.¹¹ Using our parameters for β and $E_{n,\infty}$ we find that a transition energy of 2.11 eV indeed corresponds to a conjugation length of 16–18 thiophene-rings. This is a consistency check for present data analysis.

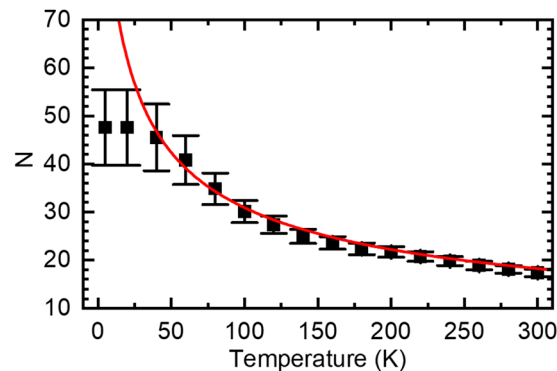


Fig. 7 Average number of thiophene rings N in a conjugated segment that gives rise to PL emission at a given temperature, calculated from eqn (4) using the data in Fig. 4(a). The red line denote the values based on the extrapolation to 0 K (dashed line in Fig. 4(a)), the black squares are based on the experimental data (black squares in Fig. 4(a)).

The concept of spectral diffusion predicts that once generated, excitons relax towards deeper states of the distribution and finally settle at a quasi-equilibrium level that is controlled by the trade-off between temperature-activated diffusion and radiative or non-radiative decay. When the chromophores are long as in a PDOPT-film, spectral diffusion can extend towards very low temperatures because, in view the parabolic dependence of the exciton energy and the chain length, the activation energy needed for transport becomes very small. Eventually, there will be a cut-off energy that translate into a maximum value of the conjugation length because ultimately excitons decay before finding another available chromophore for further energy transfer. Fig. 7 illustrates how this manifests itself in a maximum conjugation length of about 50 thiophene rings when eqn (4) is used to convert the temperature-dependent E_{0-0} values to number of coupled thiophene rings N (note that one thiophene ring $N = 2$ double bonds n).

Extrapolating both the energy of the 0–0 feature of the PL spectrum and the variance of static disorder towards $T = 0$ K yields the asymptotic value for the PL spectrum of an infinite chain in the absence of both static and dynamic disorder and should mimic the ZPL 0–0 feature of a chain matrix-isolated in a decane-glass that is resonant in absorption and emission. Indeed, Raithel *et al.* found that the standard deviations of the ZPL lines are of the order of few meV. This remaining linewidth has to be an intra-chain property related to intra-chain scattering of the excitation.

5. Conclusions

Based upon absorption and fluorescence spectra in a film of neat PDOPT, that is a thiophene chain planarized *via* side-group alignment leading to long conjugated units, we are able to rationalize the inhomogeneous line broadening in a system of linearly extended chromophores. We find that under broad excitation the PL spectrum bears out a continuous red-shift when cooling the sample from 300 K to 20 K followed by



subsequent saturation. Concomitantly the standard deviation σ of the 0–0 feature of the PL spectrum decreases from about 40 meV to 10 meV. Basically, these observations are the signature of spectral diffusion of singlet excitons which allows mapping the distribution of singlet states from which emission occurs. The intriguing aspect is that spectral diffusion extends to very low temperatures and that the ultimate PL-linewidth is as low as 10 meV, *i.e.*, only 3 times the mean standard deviation of the zero-phonon-line that had been measured on a matrix-isolated PDOPT-chromophore. We argue that this a characteristic property of a long-chain chromophore whose inhomogeneous line-broadening is the sum of three terms, (i) dynamic disorder, (ii) static disorder due to van-der-Waals-type coupling of the excited state to the random environment, and (iii) static disorder because the energy of the excited states depends on the conjugation length of the oligomer that is subject to a distribution. In particular, we found the variance of the static disorder, $\sigma_{\text{stat}}^2 = \sigma_{\text{vdW}}^2 + \sigma_{\text{CL}}^2$, to reduce in a linear fashion along with the 0–0 transition energy when the conjugation in a polymer chain segment increases. It is remarkable that that both reduce concomitantly, *i.e.* σ_{vdW} as a result of a motional narrowing effect, and σ_{CL} , as a result of the parabolic energy dependence of transition energies on inverse conjugation length. In this way, our findings elucidate and quantify the relationship between conjugation length and static disorder. Given that energetic disorder is still a key factor controlling thermally activated charge transport, knowledge on what can reduce disorder is relevant to device applications.

Our findings can have implications for the design of solar cell materials as disorder is known to limit the maximum open circuit voltage in organic solar cells.⁴⁹ Hence, the use of planar chains with long conjugation lengths is one way by which energetic disorder can be minimized. Chemical design approaches towards obtaining films with planar chains are well known. For example, rotations between repeat unit can be prevented by covalent bridges that fix the structure as in ribbon- or ladder-type frameworks, with ladder-type poly(*para*-phenylene) being the most prominent example.⁵⁰ Alternatively, non-bonding heteroatom interactions may be employed to lock the backbone.^{51,52} The results presented by us point to a third general design principle by which sterically demanding side chains force the backbone into a higher degree of coplanarity, which may be employed to other examples of conjugated polymers as well.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We thank Daniel Schiefer for synthesizing the PDOPT sample and Holger Schmalz for assistance with the Raman-Measurements. Further, we acknowledge funding from the Deutsche Forschungsgemeinschaft, KO3973/3-1, sowie IRTG 2818/1 (OPTXC) and PA3373/3-1.

References

- 1 N. R. Tummala, Z. L. Zheng, S. G. Aziz and V. Coropceanu, *et al.*, *J. Phys. Chem. Lett.*, 2015, **6**, 3657.
- 2 Z. L. Zheng, N. R. Tummala, T. H. Wang and V. Coropceanu, *et al.*, *Adv. Energy Mater.*, 2019, **9**, 1803926.
- 3 T. Linderl, T. Zechel, A. Hofmann and T. Sato, *et al.*, *Phys. Rev. Appl.*, 2020, **13**, 024061.
- 4 S. L. M. van Mensfoort, S. I. E. Vulto, R. A. J. Janssen and R. Coehoorn, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 085208.
- 5 J. Gierschner, J. Cornil and H. J. Egelhaaf, *Adv. Mater.*, 2007, **19**, 173.
- 6 K. Müllen and G. Wegner, *Electronic Materials: The Oligomer Approach*, Wiley-VCH, 1998.
- 7 S. Baderschneider, U. Scherf, J. Köhler and R. Hildner, *J. Phys. Chem. A*, 2016, **120**, 233.
- 8 J. Rissler, *Chem. Phys. Lett.*, 2004, **395**, 92.
- 9 F. M. Keheze, D. Raithel, T. Y. Wu and D. Schiefer, *et al.*, *Macromolecules*, 2017, **50**, 6829.
- 10 Y. Y. Wang, B. Heck, D. Schiefer and J. O. Agumba, *et al.*, *ACS Macro Lett.*, 2014, **3**, 881.
- 11 D. Raithel, L. Simine, S. Pickel and K. Schötz, *et al.*, *Proc. Natl. Acad. Sci. U. S. A.*, 2018, **115**, 2699.
- 12 R. Hildner, L. Winterling, U. Lemmer and U. Scherf, *et al.*, *ChemPhysChem*, 2009, **10**, 2524.
- 13 A. Köhler and H. Bässler, *Electronic Processes in Organic Semiconductors*, Wiley-VCH, 2015.
- 14 A. Amirav, U. Even and J. Jortner, *Chem. Phys. Lett.*, 1980, **72**, 16.
- 15 B. Movaghar, M. Grünewald, B. Ries and H. Bässler, *et al.*, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1986, **33**, 5545.
- 16 S. C. J. Meskers, J. Hübner, M. Oestreich and H. Bässler, *J. Phys. Chem. B*, 2001, **105**, 9139.
- 17 S. T. Hoffmann, H. Bässler, J. M. Koenen and M. Forster, *et al.*, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2010, **81**, 115103.
- 18 T. A. Papadopoulos, L. Muccioli, S. Athanasopoulos and A. B. Walker, *et al.*, *Chem. Sci.*, 2011, **2**, 1025.
- 19 S. Athanasopoulos, S. T. Hoffmann, H. Bässler and A. Köhler, *et al.*, *J. Phys. Chem. Lett.*, 2013, **4**, 1694.
- 20 N. Banerji, *J. Mater. Chem. C*, 2013, **1**, 3052.
- 21 L. M. Herz, C. Silva, A. C. Grimdale and K. Müllen, *et al.*, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2004, **70**, 165207.
- 22 N. Banerji, S. Cowan, E. Vauthey and A. J. Heeger, *J. Phys. Chem. C*, 2011, **115**, 9726.
- 23 W. Barford and M. Marcus, *J. Chem. Phys.*, 2017, **146**, 130902.
- 24 W. R. Hollingsworth, J. Lee, L. Fang and A. L. Ayzner, *ACS Energy Lett.*, 2017, **2**, 2096.
- 25 W. Barford, *Front. Phys.*, 2022, **10**, 1004042.
- 26 A. J. Sneyd, D. Beljonne and A. K. Rao, *J. Phys. Chem. Lett.*, 2022, 6820.
- 27 O. V. Mikhnenko, P. W. M. Blom and T. Q. Nguyen, *Energy Environ. Sci.*, 2015, **8**, 1867.
- 28 S. Westenhoff, W. J. Beenken, A. Yartsev and N. C. Greenham, *J. Chem. Phys.*, 2006, **125**, 154903.



- 29 S. Westenhoff, W. J. Beenken, R. H. Friend and N. C. Greenham, *et al.*, *Phys. Rev. Lett.*, 2006, **97**, 166804.
- 30 A. Stankevych, R. Saxena, A. Vakhnin, F. May, N. Kinaret, D. Andrienko, J. Genoe, H. Bäessler, A. Köhler and A. Kadashchuk, *Phys. Rev. Appl.*, 2023, **19**, 054007.
- 31 W. Kuhn, *Helv. Chim. Acta*, 1948, **31**, 1780.
- 32 D. Schiefer, T. Wen, Y. Y. Wang and P. Goursot, *et al.*, *ACS Macro Lett.*, 2014, **3**, 617.
- 33 A. Hamidi-Sakr, D. Schiefer, S. Covindarassou and L. Biniak, *et al.*, *Macromolecules*, 2016, **49**, 3452.
- 34 K. E. Aasmundtveit, E. J. Samuelsen, W. Mammo and M. Svensson, *et al.*, *Macromolecules*, 2000, **33**, 5481.
- 35 F. C. Spano, *Acc. Chem. Res.*, 2010, **43**, 429.
- 36 F. Panzer, H. Bäessler and A. Köhler, *J. Phys. Chem. Lett.*, 2017, **8**, 114.
- 37 J. Nightingale, J. Wade, D. Moia and J. Nelson, *et al.*, *J. Phys. Chem. C*, 2018, **122**, 29129.
- 38 P. Cavassin, I. Holzer, D. Tsokkou and O. Bardagot, *et al.*, *Adv. Mater.*, 2023, 2300308.
- 39 S. T. Hoffmann, S. Athanasopoulos, D. Beljonne and H. Bäessler, *et al.*, *J. Phys. Chem. C*, 2012, **116**, 16371.
- 40 H. Bäessler, *Phys. Status Solidi B*, 1993, **175**, 15.
- 41 G. N. Lewis and M. Calvin, *Chem. Rev.*, 1939, **25**, 273.
- 42 W. Barford, *J. Phys. Chem. A*, 2013, **117**, 2665.
- 43 J. Knoester, *J. Chem. Phys.*, 1993, **99**, 8466.
- 44 E. W. Knapp, *Chem. Phys.*, 1984, **85**, 73.
- 45 D. Wasserberg, P. Marsal, S. C. Meskers and R. A. Janssen, *et al.*, *J. Phys. Chem. B*, 2005, **109**, 4410.
- 46 H. Yamagata, N. J. Hestand, F. C. Spano and A. Köhler, *et al.*, *J. Chem. Phys.*, 2013, **139**, 114903.
- 47 F. C. Spano, *J. Chem. Phys.*, 2005, **122**, 234701.
- 48 H. Yamagata and F. C. Spano, *J. Chem. Phys.*, 2012, **136**, 184901.
- 49 M. Panhans, S. Hutsch, J. Benduhn and K. S. Schellhammer, *et al.*, *Nat. Commun.*, 2020, **11**, 1488.
- 50 U. Scherf, *J. Mater. Chem.*, 1999, **9**, 1853.
- 51 C. J. Mueller, E. Gann, C. R. McNeill and M. Thelakkat, *J. Mater. Chem. C*, 2015, **3**, 8916.
- 52 N. E. Jackson, B. M. Savoie, K. L. Kohlstedt and M. O. de la Cruz, *et al.*, *J. Am. Chem. Soc.*, 2013, **135**, 10475.

