

Polymer Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

One for all: Cobalt-Containing Polymethacrylates for Magnetic Ceramics, Block Copolymerization, Unexpected Electrochemistry, and Stimuli-Responsiveness

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/C. Rüttiger^{a,‡}, V. Pfeifer^{a,‡}, V. Rittscher^a, D. Stock^a, D. Scheid^a, S. Vowinkel^a, F. Roth^b, H. Didzoleit^c, B. Stühn^c, J. Elbert^{a,d}, E. Ionescu^b, and M. Gallei^{a,*}

Novel cobalt-containing homo- and diblock copolymers with poly(methyl methacrylate) (PMMA) are synthesized by atom transfer radical polymerization (ATRP) of a neutral cobalt-complex methacrylate. An efficient route for a single-step synthesis of the cobalt precursor based on easily-available starting materials followed by esterification with methacrylic acid is presented. The cobalt-methacrylate monomer is furthermore polymerized by thermal, free radical and statistical copolymerization with MMA and investigated with respect to (absolute) molar masses, polymer composition, and thermal properties. ATRP affords block copolymers as evidenced by ¹H NMR spectroscopy, size exclusion chromatography (SEC) and differential scanning calorimetry (DSC). The cobalt-containing homopolymers are investigated and tailored with respect to their thermal conversion into magnetic cobalt oxides and elemental cobalt which is evidenced by X-ray diffraction (XRD), Raman spectroscopy, and superconducting quantum interference device magnetometry (SQUID) measurements. The (reversible) electrochemistry of the cobalt-containing polymethacrylates and block copolymers thereof are thoroughly addressed by cyclic voltammetry (CV) studies. Interestingly, the prepared metalblock copolymers exhibit redox-responsiveness (both reduction and oxidation) and thus structure formation in the presence of a reduction or oxidation reagent are demonstrated by transmission electron microscopy (TEM).

Introduction

In the recent past, metal-containing polymers attracted enormous attention due to their promising combination of redox, mechanical, semi-conductive, photo-physical, optoelectronic, magnetic and catalytic properties as well as their mechanical robustness.¹⁻¹³ These polymers can either feature a metal center as integral part of the polymer main chain or the metal-containing moiety is laterally attached to the polymer chain. The vast majority of reports on metal-containing polymers deal with metallocene-based polymers, *i.e.*, metal centres sandwiched between cyclic hydrocarbon moieties, as recent synthetic pathways – mainly focussing on ferrocene monomers – led to stable and well characterized functional materials. In the 1970s Pittman and co-workers succeeded in (co)polymerizing ferrocenyl (meth)acrylates with different monomers by free radical polymerization (FRP) and anionic polymerization,¹⁴⁻¹⁷ while anionic block copolymerization was reported more recently.^{18, 19} A

breakthrough in the synthesis of metallopolymers represents the ring-opening polymerization (ROP) of strained *ansa*-metallocenophanes found by Manners and co-workers, yielding interesting main-chain metallopolymers.²⁰⁻²² Since Manners' discovery, high-molecular weight polyferrocenylsilanes (PFS) and manifold PFS-based block copolymers with interesting properties were synthesized. Notwithstanding the obstacles in the past, the synthesis of side chain metallopolymers is a field of growing interest. Excellent reviews in that field comprising the synthesis as well as novel applications for ferrocene- and cobaltocene-containing polymers given by Tang and co-workers.²³⁻²⁵ Additionally, ferrocene- and cobalt-containing metallopolymers were found to be feasible as precursor for the preparation of magnetic nanoparticles.²⁶⁻³¹ Block copolymers consist of two or more polymer segments covalently connected to each other and they have attracted enormous attention in the recent past due to their unique capability of forming fascinating nanostructures in the bulk or by self-organization in solvents.³²⁻³⁸ Therefore, applications of

block copolymers are manifold ranging, *e.g.* from fields of nanolithography, drug delivery to separation technologies. Metalblock copolymers have been used for a variety of interesting applications, which have been reviewed by Manners *et al.* very recently.³⁹ For example, Tang *et al.* reported on the successful synthesis and self-assembly of triblock copolymers featuring a poly(ferrocenyl methacrylate) block segment for the preparation of ordered iron oxides.⁴⁰

Compared to ferrocene-containing polymers, much less research is carried out in the field of cobalt-containing polymers. There, especially studies on the 18-electron cobaltocenium complex garnered a great deal of attention. The important difference compared to the isoelectronic ferrocene moiety is the presence of a charge on these complexes and corresponding metallopolymers which dictates solubility and properties. Excellent reviews within this field of research are given by Tang and co-workers.^{24, 25} Very recently, Zhang *et al.* reported on the formation of anion-responsive cobaltocenium-based polyelectrolytes with potential applications in the field of healthcare and environmental treatment.⁴¹ Neutral cobalt(I)-containing metallopolymers consisting of mixed cyclopentadienyl-cobalt-cyclobutadienyl (CpCoCb) complexes were reported by the group of Ragnogna.⁴² Recently, a reversible addition-fragmentation transfer (RAFT) polymerization of an Co(I)-acrylate derivative was used for the preparation of low molar mass cobalt-containing block copolymers.⁴³

In the present study, the preparation of the mixed CpCoCb-containing methacrylate and polymerization (free radical, copolymerization, and atom transfer radical polymerization) and block copolymerization is described. The monomer precursor (η^5 -cyclopentadienyl-4-hydroxybutan-1-on)cobalt(η^4 -tetraphenyl-cyclobutadiene) **3** and its esterification with methacrylic acid are shown in Fig. 2. The ring-opening reaction of γ -butyrolactone **2** with sodium cyclopentadienylide (NaCp, **1**) followed by the reaction with $\text{CoCl}(\text{PPh}_3)_3$ and cyclooctadiene (COD) for the preparation of mixed and stable CpCoCOD complexes was reported by Gleiter *et al.*⁴⁴ and Sigman *et al.*⁴⁵ Ragnogna and co-workers further developed a route for the synthesis of the mixed cyclopentadienyl-cobalt-cyclobutadienyl (CpCoCb) complex **3** by using a multi-step reaction with the COD-cobalt complex as intermediate.⁴³ Inspired by the synthesis of different mixed CpCoCb complexes by Anderson *et al.*,⁴⁶ we developed a more convenient single-step synthesis for derivative **3**, *i.e.* (η^5 -cyclopentadienyl-4-hydroxybutan-1-on)cobalt(η^4 -tetraphenyl-cyclobutadiene), as given in Fig. 2 (top) and as described in detail in the Experimental Section.

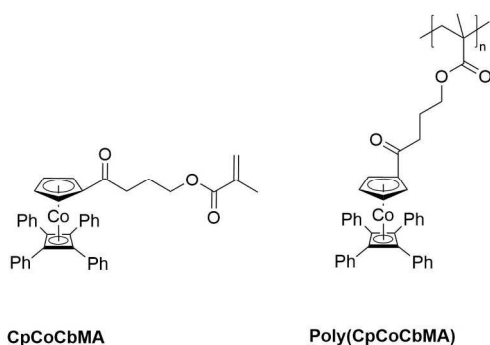


Fig. 1 The cobalt-containing methacrylate (CpCoCbMA, left) and the corresponding poly(CpCoCbMA) (right), which are investigated in this study.

In addition to the structural and thermal characterization of the synthesized homo- and diblock copolymers involving NMR analysis, size exclusion chromatography (SEC), SEC with multi-angle laser light scattering (SEC-MALLS) detector, differential scanning calorimetry (DSC), and thermal

gravimetric analysis (TGA), insights into their electrochemistry and ceramization behavior are presented. The resulting magnetic ceramic is investigated for the first time with respect to its composition and magnetic properties by X-ray diffraction, Raman spectroscopy, and superconducting quantum interference device magnetometry (SQUID). Inspired by our cyclic voltammetry studies, the cobalt-containing diblock copolymers are investigated regarding their stimuli-responsiveness towards oxidation and reducing reagents and their unprecedented structure formation as investigated by transmission electron microscopy (TEM).

3 Results and discussion

Monomer Synthesis

The synthesis of the cobalt-containing monomer precursor (η^5 -cyclopentadienyl-4-hydroxybutan-1-on)cobalt(η^4 -tetraphenyl-cyclobutadiene) **3** and its esterification with methacrylic acid are shown in Fig. 2. The ring-opening reaction of γ -butyrolactone **2** with sodium cyclopentadienylide (NaCp, **1**) followed by the reaction with $\text{CoCl}(\text{PPh}_3)_3$ and cyclooctadiene (COD) for the preparation of mixed and stable CpCoCOD complexes was reported by Gleiter *et al.*⁴⁴ and Sigman *et al.*⁴⁵ Ragnogna and co-workers further developed a route for the synthesis of the mixed cyclopentadienyl-cobalt-cyclobutadienyl (CpCoCb) complex **3** by using a multi-step reaction with the COD-cobalt complex as intermediate.⁴³ Inspired by the synthesis of different mixed CpCoCb complexes by Anderson *et al.*,⁴⁶ we developed a more convenient single-step synthesis for derivative **3**, *i.e.* (η^5 -cyclopentadienyl-4-hydroxybutan-1-on)cobalt(η^4 -tetraphenyl-cyclobutadiene), as given in Fig. 2 (top) and as described in detail in the Experimental Section.

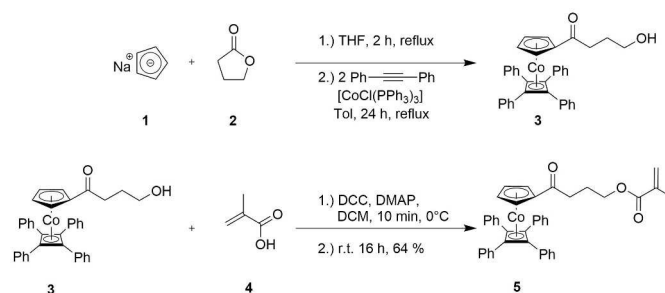


Fig. 2 One-pot synthesis of (η^5 -cyclopentadienyl-4-hydroxybutan-1-on)cobalt(η^4 -tetraphenyl-cyclobutadiene) **3** (CpCoCb) by sequential addition of given reagents (top, see Experimental Section). Steglich esterification of CpCoCb **3** with methacrylic acid **4** yielded the cobalt-methacrylate monomer **5** CpCoCbMA.

The cobalt-containing hydroxyl derivative **3** was used in a Steglich esterification protocol with methacrylic acid (see Experimental Section) in order to obtain the novel cobalt-containing methacrylate **5** (CpCoCbMA) which has not been described in literature yet. The structure of the obtained monomer **5** was supported by ^1H NMR spectroscopy (Fig. 3), ^{13}C NMR spectroscopy (Fig. S1), and electrospray ionization mass spectrometry (ESI-MS).

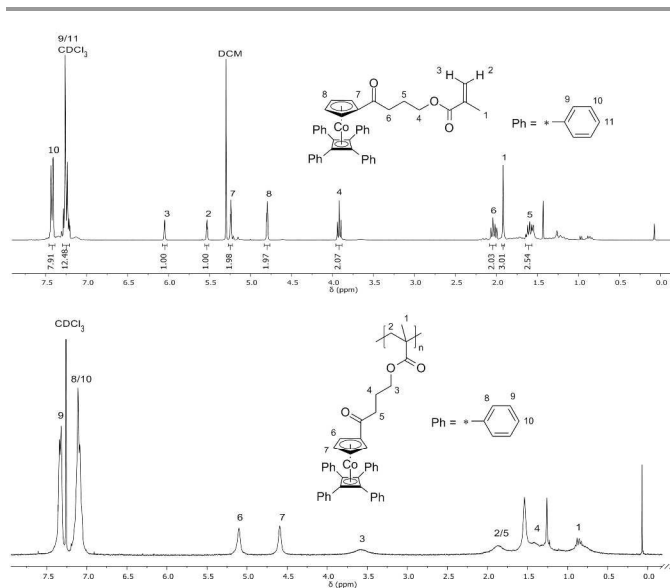


Fig. 3 ^1H NMR spectra and signal assignment of the cobalt-methacrylate monomer **5** (CpCoCbMA) (top) and of a corresponding poly(CpCoCbMA) obtained upon thermal polymerization of **5** (bottom).

Thermal and Free Radical Polymerization of CpCoCbMA

Thermal polymerization of the new cobalt-containing methacrylate monomer **5** for the preparation of poly(CpCoCbMA) was performed under vacuum at 100°C . The obtained orange solid was soluble in common organic solvents, e.g. chloroform and THF. SEC measurements are given as Fig. S2. As a result, remarkably high molar masses up to 192 kg mol^{-1} (M_n) with a polydispersity value, D , of 3.99 were obtained for SEC measurements vs. polystyrene (PS) standards. Absolute molar masses were determined for samples obtained by free radical polymerisation using azobisisobutyronitrile (AIBN) as initiator as described in the ensuing section. An exemplary ^1H NMR spectrum of the polymer sample obtained by thermally induced polymerization of monomer **5** was directly compared to the corresponding ^1H NMR spectrum of the monomer **5** in Fig. 3 (bottom). The significant signal broadening and the absence of unsaturated methacrylate proton signals proved the presence of poly(CpCoCbMA).

Free radical polymerization and copolymerization of monomer **5** with methyl methacrylate was performed by initiation with AIBN in toluene at 60°C for 24 h (see Experimental Section). The poly(CpCoCbMA) homopolymers were poured into methanol for precipitation and the resulting yellow powder was analysed by SEC measurements, NMR spectroscopy, and differential scanning calorimetry. While NMR results indicate a similar molecular structure to that of poly(CpCoCbMA) which was obtained by thermal polymerization, only a rather low apparent molar mass, i.e. 8900 g mol^{-1} (M_n), was determined by using SEC vs. PS calibration for poly(CpCoCbMA) (Fig. S3). Absolute molar masses which were determined by SEC with multi angle laser light scattering detection (SEC-MALLS) for these polymers will be described in the ensuing section. The novel

poly(CpCoCbMA) was investigated with respect to its thermal properties by DSC (Fig. S4). It can be concluded from Fig. S4 that only one glass transition temperature, T_g , was observed at $T_g=137^\circ\text{C}$, which is higher compared to that of similar cobalt-containing poly(acrylates) reported in the literature, which were obtained by RAFT polymerization ($T_g=85^\circ\text{C}$).⁴³ Additionally, radical copolymerization with methyl methacrylate (MMA) was performed as described in the Experimental Section. Results on SEC, DSC, and ^1H NMR spectroscopy measurements are given as Fig. S5, Fig. S6, and Fig. S7, respectively. Based on these results, it can be concluded that also the copolymerization of CpCoCbMA **5** with MMA was successful, as supported by a monomodal molecular weight distribution as well as the presence of a T_g value of 120°C , hence between the T_g of pure poly(CpCoCbMA) (137°C) and pure PMMA obtained by free radical polymerization (105°C).⁴⁷ Moreover, based on the corresponding ^1H NMR spectrum (Fig. S7), a PMMA content of 56 mol% and 44 mol% for poly(CpCoCbMA) could be determined proving the success of radical copolymerization of MMA and the cobalt-containing monomer CpCoCbMA **5**.

Atom Transfer Radical Polymerization of CpCoCbMA and Block Copolymer Formation

Atom transfer radical polymerization (ATRP) of CpCoCbMA **5** was carried out with 2-bromoisobutyric *tert*-butyl ester (*t*Bbib) as ATRP initiator and $[\text{Cu}^1(\text{PMDETA})\text{Br}]$ as catalyst in anisole at 80°C (see Experimental Section). The synthesis is depicted in Fig. 4 (top). As a result, narrowly distributed molecular weight distributions can be obtained for poly(CpCoCbMA) as determined by SEC measurements (Fig. S8), thus proving the feasibility of the applied ATRP protocols. Exemplarily, an apparent molar mass of 5800 g mol^{-1} was obtained by using SEC vs. PS standards.

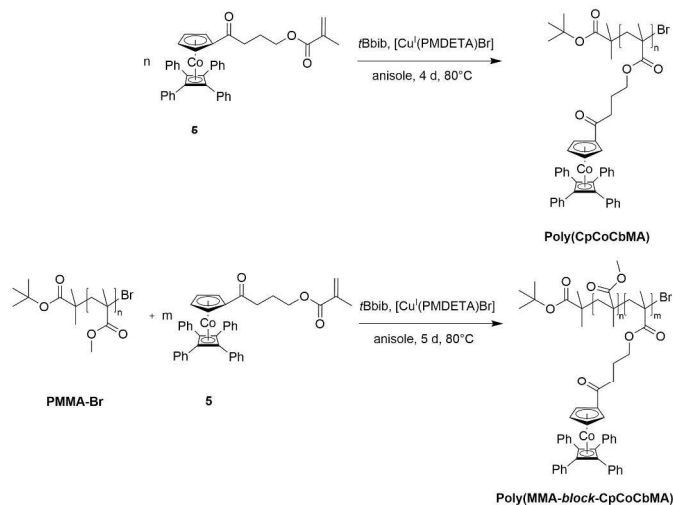


Fig. 4 Atom Transfer Radical Polymerization (ATRP) of CpCoCbMA **5** (top) and block copolymerization starting with an PMMA-Br macro-initiator (bottom) for the preparation of PMMA-*block*-P(CpCoCbMA).

Before the block copolymerization of MMA and CpCoCbMA **5** was investigated, we studied the absolute molar masses of poly(CpCoCbMA), which were obtained by free radical polymerization and ATRP. Results are compiled in Table 1 for direct comparison. It turned out that absolute molar masses for poly(CpCoCbMA) significantly differ from values obtained by SEC vs. PS standards. In other words, poly(CpCoCbMA) chains feature considerably smaller hydrodynamic volumes compared to *e.g.* PS chains of identical contour length. This is maybe due to the fact that poly(CpCoCbMA) chains are rather weakly solvated in common solvents for SEC analysis like THF. This behaviour was also found for other metallopolymers with sterically demanding pendant groups, *e.g.* polyvinylferrocene⁴⁸ or poly(2-(methacryloyloxy)ethyl ferrocenecarboxylate) (PFcMA).²⁸

Tab. 1 Comparison of relative and absolute molar masses for poly(CpCoCbMA) as obtained by free radical polymerization and ATRP.

	M_n^a (g mol ⁻¹)	M_w^a (g mol ⁻¹)	M_w^b (g mol ⁻¹)	D^c
Poly(CpCoCbMA) ^c	8 900	18 600	56 000	2.09
Poly(CpCoCbMA) ^d	4 600	5 800	12 800	1.26

^a Molar masses and D determined by using SEC measurements with PS calibration. ^b Molar masses determined by using SEC-MALLS measurements. Refractive index increment was determined to $dn/dc = 0.169$. ^c Polymer obtained by free radical polymerization with AIBN as initiator. ^d Polymer obtained by ATRP.

For the preparation of block copolymers, PMMA-Br macro initiators were prepared via ATRP using 2-bromoisobutyric *tert*-butyl ester (*t*Bbib) as initiator and [Cu^I(TMEDA)₂Br] as catalyst system in anisole at 88°C (Fig. 4, bottom, for details refer to the Experimental Section). The PMMA-Br macro initiators were precipitated in *n*-hexane, filtered and dried *in vacuo*. PMMA-Br was used for the initiation of monomer CpCoCbMA **5** in anisole in the presence of [Cu^I(PMDETA)₂Br] at 80°C. After 5 d of reaction time, the corresponding polymers were again precipitated, filtered and dried *in vacuo*. Exemplary results on block copolymerization obtained by SEC measurements for the PMMA-Br macro-initiators and the final cobalt-containing block copolymers are given as Fig. 5 (PMMA-Br, and block 1) and Fig S9 (block 2).

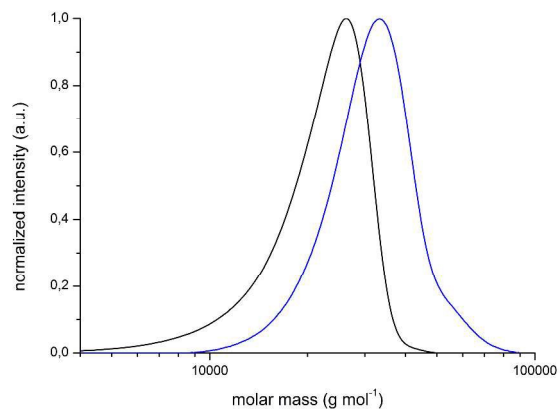


Fig. 5 Molecular weight distribution of poly(MMA-*b*-lock-CpCoCbMA) in THF (blue curve) obtained by sequential ATRP of the PMMA-Br macro-initiator (black curve) with CpCoCbMA **5**. Obtained values were calibrated against PS standards.

The compositions on the final PMMA-*b*-PCpCoCbMA block copolymers were determined by using ¹H NMR spectroscopy (Fig. S10 and Fig. S11). All results on the corresponding block copolymers are compiled in Table 2. A first evidence that these block copolymers are capable of microphase separation is due to the presence of two glass transition temperatures, *i.e.* 116°C which can be assigned to the PMMA block segment and 134°C which corresponds to poly(CpCoCbMA). The corresponding DSC differential-thermograms can be found as Fig. S12 and Fig. S13, respectively.

Tab. 2 Molar masses obtained by SEC measurements vs. PS standards for ATRP block copolymerization of MMA and CpCoCbMA.

	M_n^a (g mol ⁻¹)	M_w^a (g mol ⁻¹)	D	Comp. ^b (wt%)	T_g (°C)
PMMA-Br 1	19 600	22 600	1.15	100/0	116°C
PMMA-Br 2	9 500	12 100	1.27	100/0	116°C
Block 1	28 800	30 100	1.05	73/27	116°C/134°C
Block 2	13 000	15 000	1.15	57/43	116°C/133°C

^a Molar masses determined by using SEC measurements vs. PS calibration. ^b Comp.: Compositions were determined by using ¹H NMR spectroscopy; values are given as wt% PMMA to wt% P(CpCoCbMA).

In summary, ATRP is a feasible method for the preparation of poly(CpCoCbMA)-containing block copolymers with PMMA as first block segment. Moreover, excellent control over block copolymer composition with low values on polydispersity (D between 1.05 and 1.15) was achieved. Before the stimuli-responsiveness of the cobalt-containing block copolymers is investigated, ceramization of the corresponding cobalt-containing homopolymers and their interesting electrochemistry will be addressed in the ensuing two sections.

Thermal Conversion of Poly(CpCoCbMA) into Cobalt-containing Magnetic Ceramics

As already mentioned in the introduction, metallopolymers are excellent candidates for the preparation of advanced functional ceramics after thermal treatment. Therefore, the cobalt-containing homo polymers were investigated with respect to their thermal behaviour under different atmospheres, *i.e.* nitrogen and oxygen, by using thermal gravimetric analysis (TGA). Exemplary diagrams for the thermal treatment of poly(CpCoCbMA) either in nitrogen or oxygen atmosphere with a heating rate of 10 K min^{-1} in the range from room temperature up to 800°C are shown in Fig. 6. A similar thermal behaviour of poly(CpCoCbMA) in both atmospheres can be concluded at moderate temperatures (*i.e.*, up to ca. 430°C), with a significant weight loss starting at 320°C . However, the thermal treatment in oxygen atmosphere revealed a more pronounced weight loss up to a temperature of 520°C (black curve Fig. 6), as compared to the ceramization process performed in nitrogen atmosphere (red curve Fig. 6). Interestingly, the weight loss of poly(CpCoCbMA) occurred slower compared to the sample treated in oxygen atmosphere. Moreover, the sample treated in nitrogen atmosphere was shown to further decompose with increasing the soaking time at 800°C . Thus, 30 additional minutes annealing at 800°C resulted in an increase of the mass loss from 83.7 to 89.9 wt%. Noteworthy, the sample treated in nitrogen atmosphere showed a magnetic response with a commercially available magnet, while this was not the case for the oxygen-treated sample of poly(CpCoCbMA) after heating to 800°C . As the magnetic sample was of special interest, the nitrogen-treated sample was additionally investigated by using X-ray diffraction (XRD), Raman spectroscopy, and SQUID (superconducting quantum interference device) magnetometry, which are described in the following.

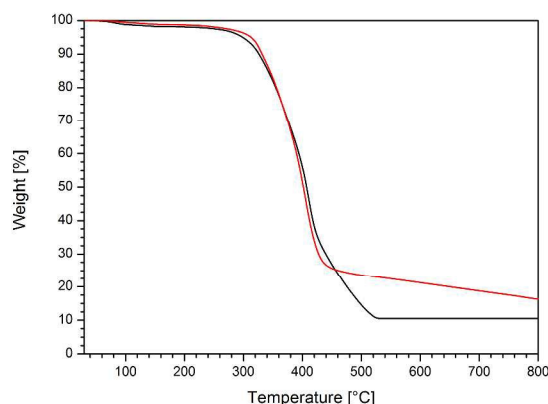


Fig. 6 TGA curves of poly(CpCoCbMA) performed with a heat rate of 10 K min^{-1} to 800°C in an oxygen (black curve) and nitrogen (red curve) atmosphere.

The X-ray diffraction (XRD) pattern of the sample obtained from poly(CpCoCbMA) heat-treated under nitrogen atmosphere at 800°C is given as Fig 7. The reflections can be assigned to three different phases comprising: 43,4 % CoO, 46,8 % Co_3O_4 and 9,9 % Co. Only strong reflections are labelled Fig 7. The full profile is analysed using the Rietveld algorithm. The CoO structure shows a cubic structure with a FM-3M space group⁴⁹ and a unit cell length of (4.3 Å). Interestingly, the Co_3O_4 contribution could be matched by a cubic system in a Fd-3m space group with a unit cell length of 8.1 Å. The elemental cobalt phase was assigned to a cubic system in a Fm-3m space group with a side length of 3.5 Å. Compared to these findings, the same sample heat-treated in oxygen atmosphere yielded pure Co_3O_4 as could be concluded from the XRD pattern (Fig. S14).

In order to gain more insights into the composition of the magnetic material, Raman spectroscopy was performed additionally. The corresponding Raman spectrum of poly(CpCoCbMA) which was thermally treated at 800°C in nitrogen atmosphere is given in Fig. 8 and indicates the presence of the spinel-type Co_3O_4 phase. Considering the spinel structure of Co_3O_4 (space group O_h^7), five vibrational modes among the total of 16 zone-center optical-phonon modes are Raman active, and were assigned to the absorption bands at 187 (F_{2g}), 465 (E_{2g}), 508 (F_{2g}), 604 (F_{2g}) and 670 (A_{1g}) cm^{-1} (Fig. 8).⁵⁰ Interestingly, Co(II) oxide was not detected unambiguously by Raman spectroscopy despite its presence was demonstrated by XRD, as the three corresponding Raman active modes thereof (at 475, 600 and 680 cm^{-1})⁵¹⁻⁵³ were weak in intensity and probably overlap with the absorption bands of the spinel-type Co_3O_4 . Similar findings related to difficulties of detecting CoO by Raman spectroscopy in the presence of Co_3O_4 were repeatedly reported in the literature.^{51, 54-57} Furthermore, the sensitivity of CoO towards the laser beam (which might induce its conversion into Co_3O_4) can be considered as an additional reason for the ambiguous detection thereof by Raman spectroscopy.^{54, 55}

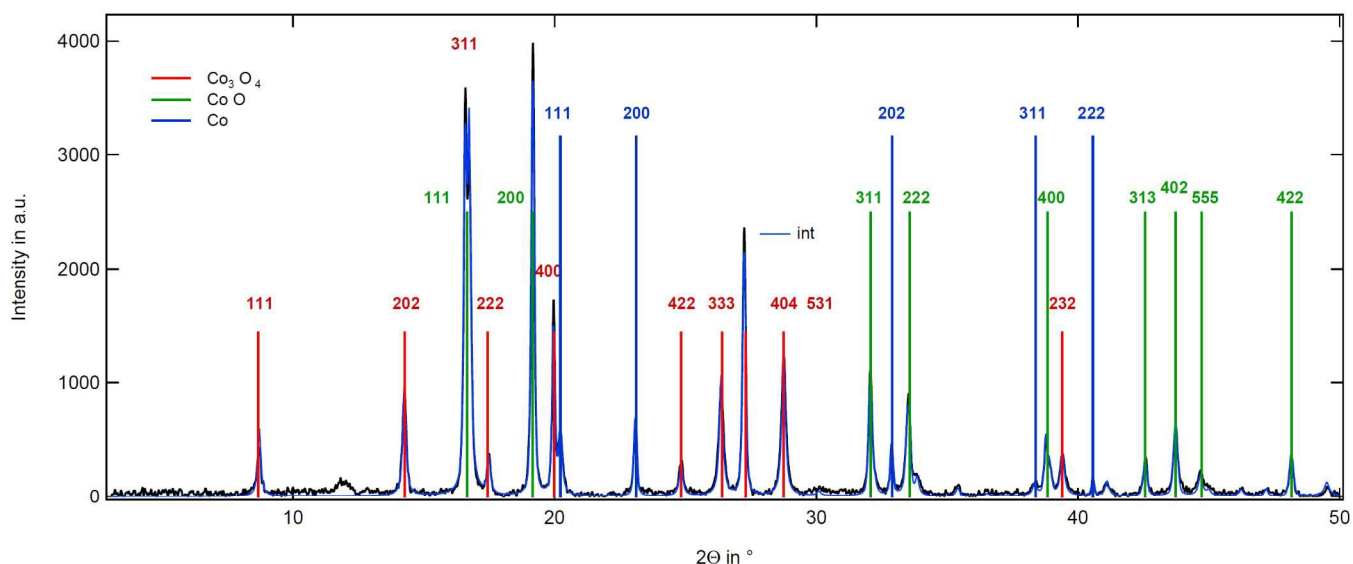


Fig. 7 XRD pattern on the magnetic material obtained by thermal treatment of poly(CpCoCbMA) samples in nitrogen atmosphere at 800°C (see text).

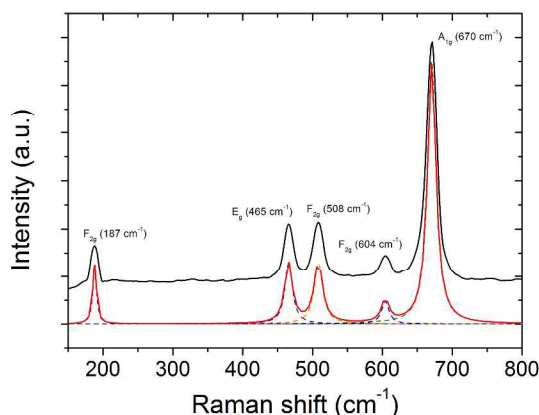


Fig. 8 Raman spectrum of the sample prepared upon pyrolysis of poly(CpCoCbMA) at 800°C in nitrogen atmosphere showing the five Raman-active optical-phonon modes of spinel-type Co_3O_4 .

These findings based on XRD and Raman spectroscopy results clearly revealed the feasibility of the herein investigated cobalt-containing metallopolymers as excellent preceramic polymer precursors for the synthesis of Co-containing magnetic ceramics. In order to investigate the magnetic properties, a SQUID measurement on the material was carried out. The corresponding SQUID measurement is shown as Fig S15. As conclusion on these data, the ceramic material indicates a ferromagnetic behaviour with an average remanence magnetisation of $M_r = 722 \text{ emu g}^{-1}$. The corresponding rather low coercivity field revealed a strength of $H_c = 30 \text{ Oe}$ for the corresponding upper and the lower curve. This value is in agreement with experiments on cobalt films.⁵⁸ Due to

instrumental limitations, a saturation magnetisation could not be determined. In summary, the herein followed convenient route paves the way to the preparation of novel polymer-derived magnetic ceramics. Moreover, Co_3O_4 -based materials are promising candidates as anode material for lithium secondary batteries due to their high electrochemical capacity and excellent recharge rates.⁵⁹ Soft polymer templating will enable the preparation of tailored architectures, adjustable material composition, and the application on doping protocols for the preparation of functional ceramics which is currently under investigation.

Electrochemistry of Poly(CpCoCbMA)

Besides the ability to form ceramics, another interesting property of metallopolymers is their fascinating redox-responsiveness due to the presence of metal centers capable of featuring several oxidation levels. While the redox chemistry of ferrocene- and cobaltocene-containing polymers has been studied leading to a plethora of fascinating applications,⁶⁰⁻⁶⁴ reports on the redox properties of neutral CpCoCb-containing polymers were not reported yet. Studies on the electrochemistry of single CpCoCb complexes showed that these compounds were capable both for reduction and oxidation.^{65, 66} For the CpCoCb without substituents at the cyclopentadienyl rings, a reversible oxidation at +0.91 V to the corresponding mono cation, followed by an irreversible oxidation at +1.55 was reported by Koelle.⁶⁶ Brotin and co-workers reported that this complex can be reduced at -2.24 V yielding an anion with the charge mainly localised on the cyclobutadienyl ligand.⁶⁵ This unprecedented possibility to switch neutral CpCoCb complexes in two ways by electrochemistry encouraged us to further study our novel cobalt polymers. Therefore, cyclic voltammetry (CV) studies of poly(CpCoCbMA) in dichloromethane were carried

out. CV curves showed a partially reversible oxidation at +1.24 V (Fig. 9, bottom) with a ratio of the peak currents $i_p^{\text{red}}/i_p^{\text{ox}} = 0.4$. The reduced reversibility after 10 CV cycles can be attributed to the low solubility of the positively charged polymer in dichloromethane leading to a precipitation of the oxidized polymer. In fact, we could observe a reversible oxidation for the monomer in dichloromethane at +1.05 V (Fig. 9 top), indicating an electrochemical reversibility of the CpCoCb/CpCoCb⁺ redox couple in poly(CpCoCbMA). The shift of this redox couple towards higher oxidation potentials of CpCoCbMA compared to the unsubstituted CpCoCb (Fig. S16) can be attributed to the electron withdrawing nature of the butanoyl substituent on the cyclopentadienyl ligand. Due to the presence of signals during CV measurements of the CpCoCb complex for reductive potentials in dichloromethane, we studied the response towards reduction for poly(CpCoCbMA) in CH₂Cl₂ (Fig. S16, bottom). A small peak at -1.45 V indicated that the reduction of the polymer to the anionic species is possible. For unsubstituted CpCoCb, we found a reversible reduction at -0.90 V (Fig. S16). In contrast to the CpCoCb/CpCoCb⁺ redox couple, no influence of the substituent on the Cp ligand on the potential of the CpCoCb⁻/CpCoCb redox couple could be observed, which is attributed to the localisation of the negative charge on the cyclobutadienyl ligand.⁶⁵

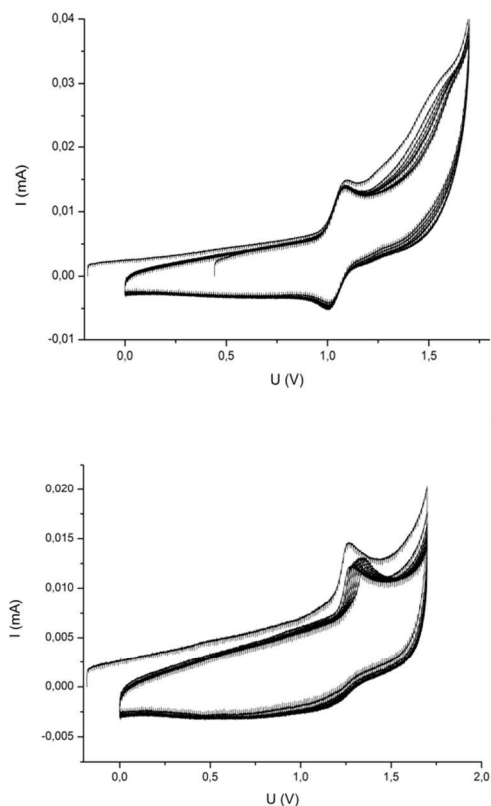


Fig. 9: Repeated cyclic voltammetry curves (10 cycles) of CpCoCbMA monomer (top) and poly(CpCoCbMA) (bottom) in CH₂Cl₂ with TBAHFP (0.1 M) as electrolyte. Scan rate was 20 mV s⁻¹.

Structure Formation of Cobalt-Containing Block Copolymers after Reaction with Redox-Reagents in Solution

To show the redox-responsive character of the novel cobalt-containing block copolymers, samples of PMMA-*b*-PCpCoCbMA (block 1) were dissolved in a small amount of CHCl₃ and treated with either a reducing or an oxidation reagent (see Experimental Section). Inspired by the results on redox waves and potentials obtained by the CV measurements as described above, NOBF₄ was used as oxidation reagent and decamethylcobaltocene (Cp*₂Co) as reducing agent for redox-controlled micellation of the cobalt-containing block copolymers. As a first hint that chemical reactions took place, the block copolymer solution changed in colour after treatment with a reducing or oxidation reagent, respectively. To gain insights into the formation of micellar aggregates, TEM images of the micellar solutions were recorded. For this purpose, the samples were drop-casted on a carbon-coated copper grid followed by drying under ambient conditions or argon flow prior to the TEM measurements. Corresponding results on TEM measurements are given in Fig. 10. Due to the presence of the metallopolymers featuring sufficient electron contrast, there was no need for staining of the samples. In the case of treating the block copolymer solution in CHCl₃ with Cp*₂Co, worm-like micellar structures were observed. Spherical and cylindrical micelles revealed diameters of approximately 20-30 nm as determined by TEM (Fig. 10, top). Noteworthy, treatment of the cobalt-containing block copolymers with NOBF₄ in order to oxidize the cobalt-containing segment yielded spherical micellar structures (with <10 nm of average diameter) as shown by TEM measurements (Fig. 10, bottom). Compared to these findings, for block copolymer solutions without the presence of reducing or oxidation reagents, no structure formation could be observed during TEM measurements which point towards well diluted block copolymers in CHCl₃. Due to the unpredictable influence of the significant amount of salts present after reduction/oxidation reactions, we did not check for reversible micelle formation.

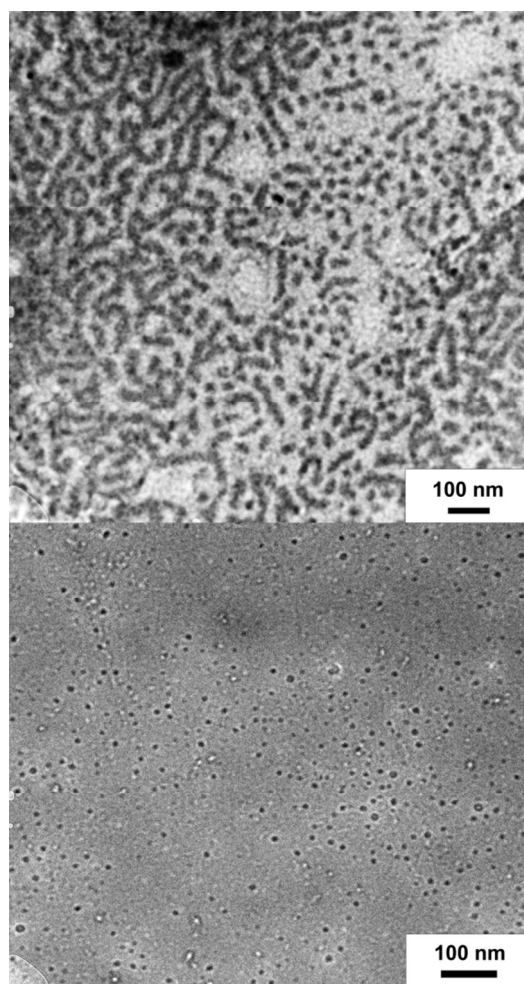


Fig. 10 TEM images of PMMA-*block*-PCpCoCbMA micelles formed in chloroform after treatment with decamethylcobaltocene (Cp*₂Co) (top) or treatment with NOBF₄ (bottom). The micelles were deposited on a carbon-coated copper grid followed by drying at ambient temperature. Scale bars correspond to 100 nm.

From the TEM images it can be concluded that worm-like micelles (reduction) or remarkably uniform spherical micelles were obtained similar to previously reported ferrocene-containing block copolymers.⁶⁷⁻⁷⁰ It is worthy to mention, that the herein investigated novel cobalt-containing block copolymers comprise a feasible platform for switching the same metallopolymer by two different chemical pathways by redox chemistry. This fascinating behavior of these cobalt-containing block copolymers is due to their capability of switching the cobalt moiety either by a reductive route or oxidative route.

Conclusions

In the current study, an efficient way for the preparation of a cobalt-containing methacrylate, *i.e.* CpCoCbMA, has been presented. The successful thermal, free radical and copolymerization (with MMA), and atom transfer radical polymerization (ATRP) has been proved by SEC, SEC-MALLS, NMR spectroscopy, and DSC measurements. Corresponding cobalt-containing homo polymers could be thermally treated in nitrogen atmosphere to yield magnetic

cobalt oxide as evidenced by XRD, Raman spectroscopy, and SQUID measurements. Efficient ATRP protocols for the preparation of poly(CpCoCbMA)-containing block copolymers with PMMA as block partner were presented. It has been showed by cyclic voltammetry (CV) that the corresponding metallopolymer underwent reversible reduction and oxidation reactions. Finally, redox-responsiveness of the diblock copolymers was evidenced by treatment with chemical reducing and oxidation reagents leading to interesting structure formation as observed by TEM measurements. Herein investigated cobalt-containing block copolymers can therefore be used as a multi-redox-responsive material. Our findings will pave the way to an addressable and highly functional platform with unprecedented and potential applications for selective release, nanolithography and for the formation of magnetic devices based on soft polymer templates.

Acknowledgements

The authors owe Prof. Alan Hatton from the Massachusetts Institute of Technology a debt of gratitude for kind discussion and help on the cyclic voltammetry results. The authors thank Jean-Christoph Jaud (group of Prof. W. Donner) from the Materials Science Department Darmstadt for performing the XRD measurement. The authors cordially thank Prof. M. Biesalski and his group (Macromolecular Chemistry and Paper Chemistry Department, TU Darmstadt) for analytical support. M.G. acknowledges the “Fonds der Chemischen Industrie” and the Max-Buchner Foundation (Dechema). J.E. would like to thank the German Academic Exchange Service (DAAD) for a Postdoctoral fellowship.

Author Contribution

MG, CR, and JE conceived the idea, CR and VP synthesized the polymers and performed measurements on polymer analytics, VR and JE investigated the electrochemistry, CR, DSch and DSt investigated micellation by TEM, SV was responsible for ceramization and TGA, FR and EI investigated the cobalt oxides by Raman spectroscopy, HD and BS were responsible for SQUID and XRD analysis and interpretation. The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Notes and references

^a Ernst-Berl-Institut für Technische und Makromolekulare Chemie, Technische Universität Darmstadt, Alarich-Weiss-Str. 4, D-64287 Darmstadt, Germany, E-mail: m.gallei@mc.tu-darmstadt.de

^b Institute of Condensed Matter Physics, Technische Universität Darmstadt, Hochschulstr. 8, D-64289 Darmstadt, Germany

^c Materials Science Department, Technische Universität Darmstadt, Jovanka-Bontschits-Str. 2, D-64287 Darmstadt, Germany

^d Author's present address: Department of Chemical Engineering, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, MA, 02139, United States

‡ These authors contributed equally.


† Electronic Supplementary Information (ESI) available: Additional data on general characterization methods, materials, monomer and

polymer synthesis, NMR spectra, molecular weight distributions, Raman spectral indicators, DSC thermograms, SQUID measurement, cyclic voltammetry studies. See DOI: 10.1039/c000000x/

1. A. S. Abd-El-Aziz and I. Manners, *Frontiers in Transition Metal-Containing Polymers*, Wiley-Interscience, Hoboken, NJ, 1997.
2. D. Wöhrle and A. D. Pomogailo, *Metal Complexes and Metals in Macromolecules: Synthesis, Structure and Properties*, Wiley-VCH, Weinheim, Germany, 2003.
3. C. E. Carraher, A. S. Abd-El-Aziz, C. Pittman, J. Sheats and M. Zeldin, *A Half Century of Metal and Metalloid Containing Polymers*, Wiley, New York, 2003.
4. I. Manners, *Synthetic Metal-Containing Polymers*, VCH, Weinheim, Germany, 2004.
5. G. R. Whittell and I. Manners, *Adv. Mater.*, 2007, **19**, 3439-3468.
6. G. R. Whittell, M. D. Hager, U. S. Schubert and I. Manners, *Nat. Mater.*, 2011, **10**, 176-188.
7. R. H. Staff, M. Gallei, M. Mazurowski, M. Rehahn, R. Berger, K. Landfester and D. Crespy, *ACS Nano*, 2012, **6**, 9042-9049.
8. A. S. Abd-El-Aziz and E. A. Strohm, *Polymer*, 2012, **53**, 4879-4921.
9. J. Elbert, M. Gallei, C. Rüttiger, A. Brunsen, H. Didzoleit, B. Stühn and M. Rehahn, *Organometallics*, 2013, **32**, 5873-5878.
10. M. Gallei, *Macromol. Chem. Phys.*, 2014, **215**, 699-704.
11. A. S. Abd-El-Aziz, C. Agatemer and N. Etkin, *Macromol. Rapid Commun.*, 2014, **35**, 513-559.
12. J. Elbert, F. Krohm, C. Rüttiger, S. Kienle, H. Didzoleit, B. N. Balzer, T. Hugel, B. Stühn, M. Gallei and A. Brunsen, *Adv. Funct. Mater.*, 2014, **24**, 1591-1601.
13. A. D. Russell, R. A. Musgrave, L. K. Stoll, P. Choi, H. Qiu and I. Manners, *J. Organomet. Chem.*, 2015, **784**, 24-30.
14. C. U. Pittman, J. C. Lai and D. P. Vanderpool, *Macromolecules* 1970, **3**, 105.
15. C. U. Pittman and A. Hirao, *J. Polym. Sci., Polym. Chem. Ed.*, 1977, **15**, 1677.
16. C. U. Pittman and A. Hirao, *J. Polym. Sci., Polym. Chem. Ed.*, 1978, **16**, 1197.
17. C. U. Pittman and C. C. Lin, *J. Polym. Sci., Polym. Chem. Ed.*, 1979, **17**, 271.
18. M. Gallei, B. V. K. J. Schmidt, R. Klein and M. Rehahn, *Macromol. Rap. Comm.*, 2009, **30**, 1463-1469.
19. M. Gallei, S. Tockner, R. Klein and M. Rehahn, *Macromol. Rapid Commun.*, 2010, **31**, 889-896.
20. D. A. Foucher, B.-Z. Tang and I. Manners, *J. Am. Chem. Soc.*, 1992, **114**, 6246-6248.
21. I. Manners, *Can. J. Chem.*, 1998, **76**, 371-381.
22. V. Bellas and M. Rehahn, *Angew. Chem. Int. Ed.*, 2007, **46**, 5082-5104.
23. C. G. Hardy, L. Ren, T. C. Tamboue and C. Tang, *J. Polym. Sci., Part A: Polym. Chem.*, 2011, **49**, 1409-1420.
24. C. G. Hardy, L. Ren, J. Zhang and C. Tang, *Israel J. Chem.*, 2012, **52**, 230.
25. C. G. Hardy, J. Zhang, Y. Yan, L. Ren and C. Tang, *Prog. Polym. Sci.*, 2014, **39**, 1742-1796.
26. K. Temple, K. Kulbaba, K. N. Power-Billard, I. Manners, K. A. Leach, T. Xu, T. P. Russell and C. J. Hawker, *Adv. Mater.*, 2003, **15**, 297-300.
27. K. R. Thomas, A. Ionescu, J. Gwyther, I. Manners, C. H. W. Barnes, U. Steiner and E. Sivaniah, *J. Appl. Phys.*, 2011, **109**, 073904.
28. M. Mazurowski, M. Gallei, J. Li, H. Didzoleit, B. Stühn and M. Rehahn, *Macromolecules*, 2012, **45**, 8970-8981.
29. D. Scheid, G. Cherkashinin, E. Ionescu and M. Gallei, *Langmuir*, 2014, **30**, 1204-1209.
30. J. Elbert, H. Didzoleit, C. Fasel, E. Ionescu, R. Riedel, B. Stühn and M. Gallei, *Macromol. Rapid Commun.*, 2015, **36**, 597-603.
31. S. Kaur, M. Gallei and E. Ionescu, *Adv. Polym. Sci.*, 2015, **267**, 143-185.
32. I. W. Hamley, *The Physics of Block Copolymers*, Oxford University Press, Oxford, 1998.
33. M. Lazzari, G. Liu and S. Lecommandoux, *Block Copolymers in Nanoscience*, Wiley-VCH, Weinheim, 2006.
34. N. A. Lynd, A. J. Meuler and M. A. Hillmyer, *Progr. Polym. Sci.*, 2008, **33**, 875-893.
35. H.-C. Kim, S.-M. Park and W. D. Hinsberg, *Chem. Rev.*, 2010, **110**, 146-177.
36. D. Klinger, M. J. Robb, J. M. Spruell, N. A. Lynd, C. J. Hawker and L. A. Connal, *Polym. Chem.*, 2013, **4**, 5038-5042.
37. R. C. Hayward and D. J. Pochan, *Macromolecules*, 2010, **43**, 3577-3584.
38. F. H. Schacher, P. A. Rugar and I. Manners, *Angew. Chem. Int. Ed.*, 2012, **51**, 7898-7921.
39. J. Zhou, G. R. Whittell and I. Manners, *Macromolecules*, 2014, **47**, 3529-3543.
40. C. G. Hardy, L. Ren, S. Ma and C. Tang, *Chem. Commun.*, 2013, **49**, 4373-4375.
41. J. Zhang, J. Yan, P. Pageni, Y. Yan, A. Wirth, Y. P. Chen, Y. Qiao, Q. Wang, A. W. Decho and C. Tang, *Sci Rep*, 2015, **5**, 11914.
42. P. Chadha and P. J. Ragogna, *Chem. Commun.*, 2011, **47**, 5301-5303.
43. M. Hadadpour, Y. Liu, P. Chadha and P. J. Ragogna, *Macromolecules*, 2014, **47**, 6207-6217.
44. R. Gleiter and G. Pflästerer, *Organomet.*, 1993, **12**, 1886-1889.
45. M. S. Sigman, A. W. Fatland and B. E. Eaton, *J. Am. Chem. Soc.*, 1998, **120**.
46. C. E. Anderson, L. E. Overman, C. J. Richards, M. P. Watson and N. White, *Org. Synth.*, 2007, **84**, 139-147.
47. A. Faldi, M. Tirrell, T. P. Lodge and E. v. Meerwall, *Macromolecules*, 1994, **27**, 4184-4192.
48. M. Gallei, R. Klein and M. Rehahn, *Macromolecules* 2010, **43**, 1844-1854.
49. W. R. W. G., *Crystal Structures*, Second edition edn., Interscience Publishers, New York, 1963.
50. V. G. Hadjiev, M. N. Iliev and I. V. Vergilov, *J. Phys. C Solid State*, 1988, **21**, L199-L201.
51. D. Gallant, M. Pezolet and S. Simard, *J. Phys. Chem. B*, 2006, **110**, 6871-6880.
52. C. K. Xu, Y. K. Liu, G. D. Xu and G. H. Wang, *Chem. Phys. Lett.*, 2002, **366**, 567-571.
53. C. A. Melendres and S. Xu, *J. Electrochem. Soc.*, 1984, **131**, 2239-2243.
54. H. C. Choi, Y. M. Jung, I. Noda and S. B. Kim, *J. Phys. Chem. B*, 2003, **107**, 5806-5811.
55. J. Llorca, P. R. de la Piscina, J. A. Dalmon and N. Homs, *Chem. Mater.*, 2004, **16**, 3573-3578.
56. C. W. Tang, C. B. Wang and S. H. Chien, *Thermochim. Acta*, 2008, **473**, 68-73.
57. J. S. Gwag and Y. Sohn, *B Korean Chem. Soc.*, 2012, **33**, 505-510.
58. H. Luo, D. Wang, J. He and Y. Lu, *J. Phys. Chem. B*, 2005, **109**, 1919-1922.
59. P. Poizot, S. Laruelle, S. Grugeon, L. Dupont and J.-M. Tarascon, *Nature*, 2000, **407**, 496-499.
60. Y. Ma, W.-F. Dong, M. A. Hempenius, H. Möhwald and G. J. Vancso, *Nat. Mat.*, 2006, **5**, 724-729.
61. X. Feng, H. Wu, X. Sui, M. A. Hempenius and G. Julius Vancso, *Europ. Polym. J.*, 2015, **72**, 535-542.
62. L. Ren, C. G. Hardy, S. Tang, D. B. Doxie, N. Hamidi and C. Tang, *Macromolecules*, 2010, **43**, 9304-9310.
63. K. Zhang, X. Feng, X. Sui, M. A. Hempenius and G. J. Vancso, *Angew. Chem. Int. Ed. Engl.*, 2014, DOI: 10.1002/anie.201408010.
64. R. H. Staff, M. Gallei, K. Landfester and D. Crespy, *Macromolecules*, 2014, **47**, 4876-4883.
65. T. Brotin, L. Pospíšil, J. Fiedler, B. T. King and J. Michl, *J. Phys. Chem. B*, 1998, **102**, 10062-10070.
66. U. Koelle, *Inorg. Chim. Acta*, 1981, **47**, 13-18.
67. N. McGrath, F. H. Schacher, H. Qiu, S. Mann, M. A. Winnik and I. Manners, *Polym. Chem.*, 2014, **5**, 1923-1929.
68. Z. M. Hudson, C. E. Boott, M. E. Robinson, P. A. Rugar, M. A. Winnik and I. Manners, *Nat. Chem.*, 2014, **6**, 893-898.

69. C. Tonhauser, M. Mazurowski, M. Rehahn, M. Gallei and H. Frey, *Macromolecules*, 2012, **45**, 3409-3418.
70. J. Morsbach, A. Natalello, J. Elbert, S. Winzen, A. Kroeger, H. Frey and M. Gallei, *Organomet.*, 2013, **32**, 6033-6039.
71. Y. Watatsuki and H. Yamazaki, *Inorg. Synth.*, 1989, **26**, 189-200.

ToC Graphics

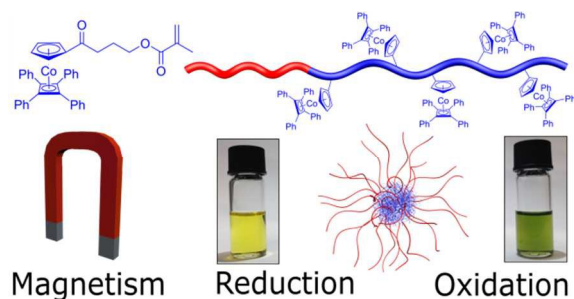

ToC Entry

Functional cobalt-containing polymers are prepared and tailored with respect to tailored block copolymers, unprecedented electrochemistry, and for usability as preceramic polymers for magnetic cobalt-based materials. Due to the reduction and oxidation responsiveness of the cobalt moiety as part of the block copolymer architecture, structure formation in organic solvents is shown to be switchable.