



**Synthesis, characterisation and Pickering emulsifier performance of poly(stearyl methacrylate)-poly(N-2-(methacryloyloxy)ethyl pyrrolidone) diblock copolymer nano-objects via RAFT dispersion polymerisation in n-dodecane**

Journal:	<i>Polymer Chemistry</i>
Manuscript ID	PY-ART-01-2016-000138.R1
Article Type:	Paper
Date Submitted by the Author:	09-Feb-2016
Complete List of Authors:	Cunningham, Victoria; University of Sheffield, Chemistry Armes, Steven; University of Sheffield, Department of Chemistry Musa, Osama; Ashland Inc.,



Journal Name

ARTICLE

## Synthesis, characterisation and Pickering emulsifier performance of poly(stearyl methacrylate)-poly(*N*-2-(methacryloyloxy)ethyl pyrrolidone) diblock copolymer nano-objects via RAFT dispersion polymerisation in *n*-dodecane

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

V. J. Cunningham,<sup>a</sup> S. P. Armes,<sup>a</sup> \* and O. M. Musa<sup>b</sup>

A near-monodisperse poly(stearyl methacrylate) macromolecular chain transfer agent (PSMA macro-CTA) was prepared via reversible addition-fragmentation chain transfer (RAFT) solution polymerisation in toluene. This PSMA macro-CTA was then utilised as a stabiliser block for the RAFT dispersion polymerisation of a highly polar monomer, *N*-2-(methacryloyloxy)ethyl pyrrolidone (NMEP), in *n*-dodecane at 90 °C. <sup>1</sup>H NMR studies confirmed that the rate of NMEP polymerisation was significantly faster than that of a non-polar monomer (benzyl methacrylate, BzMA) under the same conditions. For example, when targeting a PSMA<sub>14</sub>-PNMEP<sub>100</sub> diblock copolymer, more than 99% NMEP conversion was achieved within 30 min, whereas only 19% BzMA conversion was obtained on the same time scale for the corresponding PSMA<sub>14</sub>-PBzMA<sub>100</sub> synthesis. The resulting PSMA-PNMEP diblock copolymer chains underwent polymerisation-induced self-assembly (PISA) during growth of the insoluble PNMEP block to form either spherical micelles, highly anisotropic worms or polydisperse vesicles, depending on the target DP of the PNMEP chains. Systematic variation of this latter parameter, along with the solids content, allowed the construction of a phase diagram which enabled pure morphologies to be reproducibly targeted. Syntheses conducted at 10% w/w solids led to the formation of kinetically-trapped spheres. A monotonic increase in particle diameter with PNMEP DP was observed for such PISA syntheses, with particle diameters of up to 462 nm being obtained for PSMA<sub>14</sub>-PNMEP<sub>960</sub>. Increasing the copolymer concentration to 15% w/w solids led to worm-like micelles, while vesicles were obtained at 27.5% w/w solids. High (≥ 95%) NMEP conversions were achieved in all cases and 3:1 chloroform/methanol GPC analysis indicated relatively high blocking efficiencies. However, relatively broad molecular weight distributions ( $M_w/M_n > 1.50$ ) were observed when targeting PNMEP DPs greater than 150. This indicates either light branching caused by the presence of a low level of dimethacrylate impurity and/or chain transfer to polymer. Finally, PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres were evaluated as Pickering emulsifiers. Unexpectedly, it was found that either water-in-oil or oil-in-water Pickering emulsions could be obtained depending on the shear rate employed for homogenisation. Further investigation suggested that high shear rates lead to *in situ* inversion of the initial hydrophobic PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres to form hydrophilic PNMEP<sub>49</sub>-PSMA<sub>14</sub> spheres.

### Introduction

It is well-known that AB diblock copolymers undergo self-assembly both in the solid state and also in solution.<sup>1–3</sup> In the latter case, a remarkably diverse range of copolymer morphologies has been reported, including spheres,<sup>4</sup> worms<sup>5, 6</sup> or vesicles.<sup>7</sup> Typically, the copolymer chains are first prepared in a non-selective solvent and then subjected to either a gradual change in solvency or a pH switch in a separate step, which is typically undertaken in dilute solution.

In recent years, polymerisation-induced self-assembly (PISA) of diblock copolymers in a solvent that is selective for the growing second block has become increasingly popular.<sup>8–10</sup> PISA offers two decisive advantages over traditional processing methods:<sup>11</sup> (i) syntheses can be conducted at up to 50% w/w solids<sup>12, 13</sup> and (ii) diblock copolymer nanoparticles are obtained directly, without requiring any post-polymerisation processing steps. When

combined with PISA, controlled radical polymerisation techniques such as atom transfer radical polymerisation (ATRP)<sup>14, 15</sup> or reversible addition-fragmentation chain transfer (RAFT) polymerisation<sup>16–19</sup> have enabled the preparation of a wide range of well-defined nanoparticles.<sup>10, 20, 21</sup> In particular, RAFT *dispersion* polymerisation allows the efficient synthesis of pure spherical, worm-like or vesicular morphologies in aqueous,<sup>22–25</sup> alcoholic<sup>26–29</sup> or non-polar media<sup>13, 30–36</sup> as well as ionic liquids.<sup>37</sup>

Of particular relevance to the present work is the RAFT-mediated synthesis of well-defined poly(lauryl methacrylate)-poly(benzyl methacrylate) (PLMA-PBzMA) diblock copolymer nanoparticles in *n*-alkanes.<sup>33</sup> Fielding et al. reported that using a relatively long PLMA macromolecular chain transfer agent (macro-CTA) only led to spherical nanoparticles regardless of the target PBzMA DP, whereas using a relatively short PLMA macro-CTA enabled the production of spherical, worm-like or vesicular nanoparticles in *n*-heptane. Switching the solvent to *n*-dodecane allowed a detailed study of the thermo-responsive behaviour of PLMA<sub>16</sub>-PBzMA<sub>37</sub> diblock copolymer worms.<sup>34</sup> Heating from 20 °C to 90 °C led to a worm-to-sphere order-order transition as a result of surface plasticisation of


<sup>a</sup> Department of Chemistry, University of Sheffield, Brook Hill, Sheffield, South Yorkshire, S3 7HF, UK.

<sup>b</sup> Ashland Specialty Ingredients, 1005 US 202/206, Bridgewater, NJ 08807, USA.

\* Author to whom correspondence should be addressed

(s.p.ames@sheffield.ac.uk).

Electronic Supplementary Information (ESI) available: PSMA<sub>14</sub>-PBzMA<sub>95</sub> experimental details, assigned NMR, analysis of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblocks prepared at 20% w/w and further Pickering emulsion data. See DOI: 10.1039/x0xx00000x

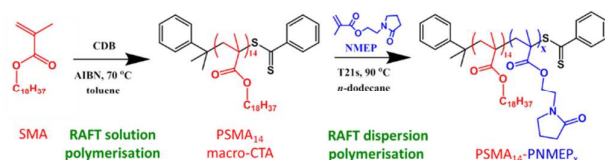

**Scheme 1.** (i) Synthesis of a PSMA<sub>14</sub> macro-CTA by RAFT solution polymerisation of SMA followed by (ii) the preparation of PSMA<sub>14</sub>-PNMEP<sub>x</sub> nano-objects via RAFT dispersion polymerisation of NMEP in *n*-dodecane.

the worm cores by the hot solvent, which causes a subtle change in the packing parameter,  $P$ .<sup>38</sup> More recently, Derry and co-workers used a similar PLMA-PBzMA formulation to target spherical nanoparticles via a highly convenient one-pot protocol in industrially-relevant solvents such as mineral oil or a poly( $\alpha$ -olefin) at up to 50% w/w solids.<sup>13</sup>

In the present work, we describe the synthesis of a range of new poly(stearyl methacrylate)-poly(*N*-2-(methacryloyloxy)ethyl pyrrolidone) (PSMA-PNMEP) diblock copolymer nano-objects via RAFT dispersion polymerisation of NMEP in *n*-dodecane, see Figure 1. The diblock copolymer chains are characterised by <sup>1</sup>H NMR and gel permeation chromatography (GPC), while dynamic light scattering (DLS) and transmission electron microscopy (TEM) has been used to assess the particle size and morphology. A phase diagram has been constructed to enable pure spherical micelles, worm-like micelles or vesicles to be reproducibly targeted. In addition, selected examples of PSMA-PNMEP spheres have been examined as putative Pickering emulsifiers.

## Experimental

### Materials

Stearyl methacrylate (SMA), cumyl dithiobenzoate (CDB) and *n*-dodecane were purchased from Sigma-Aldrich (UK) and were used as received. *N*-2-(Methacryloyloxy)ethyl pyrrolidone (NMEP, 96% purity) was donated by Ashland Specialty Ingredients (USA) and was used without further purification. Azobisisobutyronitrile (AIBN) was purchased from Molekula (Dorset, UK). *tert*-Butyl peroxy-2-ethylhexanoate (T21s) was purchased from AkzoNobel (The Netherlands). CD<sub>2</sub>Cl<sub>2</sub> was purchased from Goss Scientific Ltd., (UK) and CDCl<sub>3</sub> was purchased from VWR chemicals (UK). All other solvents were purchased from Fisher Scientific (Loughborough, UK) and were used as received.

### Preparation of PSMA<sub>14</sub> macro-CTA

SMA (33.4765 g, 0.099 mol), CDB RAFT agent (5.1690 g, 19 mmol; target degree of polymerisation, DP = 5) and AIBN (0.6233 g, 3.8 mmol; CTA/initiator molar ratio = 5.0) were weighed into a 250 ml round-bottomed flask. Toluene (58 ml) was deoxygenated separately with nitrogen for 30 min prior to addition to the other reagents. The reaction solution was stirred and degassed in an ice bath for a further 30 min, before placing in an oil bath at 70 °C. The polymerisation was allowed to proceed for 10 h, resulting in a final monomer conversion of 80 % as judged by <sup>1</sup>H NMR. The crude homopolymer was purified by precipitating into a ten-fold excess of ethanol. This purification step was repeated twice to afford a pure PSMA macro-CTA (21.6 g, < 1 % monomer remaining). The mean degree of polymerisation was calculated to be 14, as judged by <sup>1</sup>H NMR spectroscopy by comparing the integrated aromatic CDB

proton signal at 7.0-8.0 ppm with that assigned to the two oxymethylene PSMA protons at 3.6-4.2 ppm. GPC analysis using a 3:1 v/v chloroform/methanol mixed eluent indicated an  $M_n$  of 7,500 g mol<sup>-1</sup> and an  $M_w/M_n$  of 1.12 (vs. a series of near-monodisperse poly(methyl methacrylate) calibration standards).

### Synthesis of PSMA<sub>14</sub>-PNMEP<sub>x</sub> via RAFT dispersion polymerisation of SMA

A typical protocol for the synthesis of PSMA<sub>14</sub>-PNMEP<sub>98</sub> diblock copolymer nanoparticles was as follows: PSMA<sub>14</sub> macro-CTA (0.0706 g), NMEP (0.2787 g, 1.413 mmol; target DP = 100), T21s (0.755 mg, 3.49  $\mu$ mol; dissolved at 10% v/v in *n*-dodecane; CTA/T21s molar ratio = 4.0) were dissolved in *n*-dodecane (4.1 ml, 10% w/w) in a 25 ml round-bottomed flask. The reaction mixture was sealed and purged with nitrogen for 30 min, prior to immersion in an oil bath set at 90 °C for 2 h. The resulting copolymer was analysed by GPC using a 3:1 chloroform/methanol mixed eluent ( $M_n$  = 49,600 g mol<sup>-1</sup>,  $M_w/M_n$  = 1.19 vs. PMMA standards). <sup>1</sup>H NMR spectroscopy analysis of the final reaction solution diluted approximately ten-fold in CDCl<sub>3</sub> indicated 98% NMEP conversion. DLS studies conducted on a 0.20% w/w copolymer dispersion indicated an intensity-average particle diameter of 36 nm (DLS polydispersity, PDI = 0.01). Other diblock copolymer compositions were targeted by adjusting the NMEP/PSMA<sub>14</sub> macro-CTA molar ratio and/or by varying the volume of solvent in the PISA formulation.

### Preparation of Pickering emulsions using PSMA<sub>14</sub>-PNMEP<sub>49</sub> spherical nanoparticles

Water (2.0 ml) was homogenized with 2.0 ml of a 0.0675 – 2.50% w/w PSMA<sub>14</sub>-PNMEP<sub>49</sub> diblock copolymer dispersion in *n*-dodecane for 2 min at 20 °C using an IKA Ultra-Turrax T-18 homogeniser equipped with a 10 mm dispersing tool. The shear rate was systematically varied between 3 500 rpm and 24 000 rpm.

### Copolymer characterisation

**<sup>1</sup>H NMR Spectroscopy.** All <sup>1</sup>H NMR spectra were recorded at 20 °C in either CD<sub>2</sub>Cl<sub>2</sub> or CDCl<sub>3</sub> using a 400 MHz Bruker Avance-400 spectrometer with 64 scans being averaged per spectrum.

**Gel Permeation Chromatography (GPC).** The molecular weights and polydispersities of the PSMA<sub>14</sub> macro-CTA and PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers were obtained using a GPC set-up comprising a Hewlett Packard HP1090 Liquid Chromatograph pump unit and two Polymer Laboratories PL gel 5  $\mu$ m 'Mixed C' columns connected in series with a guard column at 40 °C connected to a Gilson Model 131 refractive index detector. The eluent was a 3:1 v/v% chloroform/methanol mixture containing 2 mM LiBr at a flow rate of 1.0 ml min<sup>-1</sup>. A series of near-monodisperse poly(methyl methacrylate) (PMMA) standards were used for calibration. Data analysis was carried out using Cirrus GPC software supplied by Agilent.

**Dynamic Light Scattering (DLS).** The intensity-average hydrodynamic diameter of each batch of nanoparticles was determined at 25 °C using a Malvern Zetasizer NanoZS instrument at a scattering angle of 173°. Dilute dispersions (0.20% w/w) in *n*-heptane were analysed using quartz cuvettes and data were averaged over three consecutive runs.

**Table 1.** Conversions, Molecular Weights ( $M_n$ ), Polydispersities ( $M_w/M_n$ ), Mean DLS and TEM diameters obtained for PSMA<sub>14</sub>-PNMEP<sub>x</sub> (or S<sub>14</sub>-N<sub>x</sub>) Diblock Copolymer Nanoparticles prepared at Various Solids Content and the corresponding PSMA<sub>14</sub> Macro-CTA.

	Diblock Composition	Conversion <sup>a</sup> (%)	Solids content (% w/w)	GPC <sup>b</sup>		Particle diameter
				$M_n$ (kg mol <sup>-1</sup> )	$M_w/M_n$	DLS <sup>c</sup> (nm)
1	S <sub>14</sub>	80	40	7.5	1.12	N/A
2	S <sub>14</sub> -N <sub>49</sub>	98	10	30.1	1.15	23 (0.205)
3	S <sub>14</sub> -N <sub>74</sub>	99	10	40.5	1.14	30 (0.028)
4	S <sub>14</sub> -N <sub>98</sub>	98	10	49.6	1.19	36 (0.035)
5	S <sub>14</sub> -N <sub>124</sub>	99	10	60.1	1.19	42 (0.034)
6	S <sub>14</sub> -N <sub>149</sub>	99	10	72.5	1.36	47 (0.054)
7	S <sub>14</sub> -N <sub>168</sub>	96	10	83.8	1.63	56 (0.008)
8	S <sub>14</sub> -N <sub>198</sub>	99	10	95.0	1.64	62 (0.015)
9	S <sub>14</sub> -N <sub>216</sub>	96	10	107.0	1.92	76 (0.025)
10	S <sub>14</sub> -N <sub>245</sub>	98	10	109.8	2.85	95 (0.005)
11	S <sub>14</sub> -N <sub>270</sub>	98	10	Not determined	Not determined	153 (0.006)
12	S <sub>14</sub> -N <sub>291</sub>	97	10	Not determined	Not determined	173 (0.006)
13	S <sub>14</sub> -N <sub>392</sub>	98	10	Not determined	Not determined	274 (0.028)
14	S <sub>14</sub> -N <sub>485</sub>	97	10	Not determined	Not determined	340 (0.035)
15	S <sub>14</sub> -N <sub>960</sub>	96	10	Not determined	Not determined	462 (0.010)

a. Monomer conversion determined by <sup>1</sup>H NMR spectroscopy in CDCl<sub>3</sub>.

b. Determined by 3:1 v/v chloroform/methanol GPC against PMMA calibration standards using a refractive index detector.

c. The number in brackets refers to the DLS polydispersity

**Transmission Electron Microscopy (TEM).** Copper/palladium TEM grids (Agar Scientific, UK) were coated in-house to yield a thin film of amorphous carbon. Dilute dispersions (0.20% w/w in *n*-heptane, 10.0 μL) were placed on the carbon-coated grids and left for 30 min to allow solvent evaporation. The grids were exposed to ruthenium(VIII) oxide vapour for 7 min at 20 °C prior to analysis. Imaging was performed using a Philips CM100 instrument operating at 100 kV and equipped with a Gatan 1 k CCD camera.

The ruthenium(VIII) oxide was prepared as follows: ruthenium(IV) oxide (0.30 g) was added to water (50 g) to form a black slurry; addition of sodium periodate (2.0 g) with stirring produced a yellow solution of ruthenium (VIII) oxide within 1 min.

**Optical Microscopy.** Optical microscopy images of emulsion droplets were recorded using a Motic DMBA300 digital biological microscope equipped with a built-in camera and Motic Images Plus 2.0 ML software.

**Laser Diffraction.** Emulsions were sized using a Malvern Mastersizer 2000 instrument equipped with a small volume Hydro 2000SM sample dispersion unit (ca. 50 ml), a HeNe laser operating at 633 nm, and a solid-state blue laser operating at 466 nm. The stirring rate was adjusted to 1 000 rpm in order to avoid creaming of the emulsion during analysis. After each measurement, the cell was rinsed once with ethanol, followed by two rinses with distilled water; the glass walls of the cell were carefully wiped with tissue to avoid cross-contamination and the laser was aligned centrally to the detector prior to data acquisition.


## Results and discussion

### Synthesis of PSMA macro-CTA via RAFT solution polymerisation


A PSMA macro-CTA was synthesised via RAFT solution polymerisation of SMA in toluene at 70 °C using cumyl dithiobenzoate (CDB) as a chain transfer agent (Scheme 1). The reaction was allowed to proceed for 10 h before being quenched; <sup>1</sup>H NMR spectroscopy indicated 80% conversion and a mean degree of polymerisation (DP) of 14 after purification. GPC analysis of the purified PSMA macro-CTA using a 3:1 v/v chloroform/methanol mixed eluent indicated a  $M_n$  of 7,500 g mol<sup>-1</sup> with an  $M_w/M_n$  of 1.12, which suggested good control for this pseudo-living polymerisation. A self-blocking chain extension experiment with a second charge of SMA monomer was used to examine the chain-end fidelity of the PSMA<sub>14</sub> macro-CTA. GPC analysis of the resulting PSMA<sub>14</sub>-PSMA<sub>87</sub> diblock copolymer confirmed a high blocking efficiency for the PSMA<sub>14</sub> macro-CTA (see Figure S1 in the ESI). This indicated high RAFT chain-end fidelity.

### Kinetics of the RAFT dispersion polymerisation of NMEP targeting PSMA<sub>14</sub>-PNMEP<sub>100</sub> at 20% w/w solids

A kinetic study of the chain extension of the PSMA<sub>14</sub> macro-CTA via RAFT dispersion polymerisation of NMEP in *n*-dodecane at 90 °C was conducted using a macro-CTA/initiator molar ratio of 4.0 (Scheme 1). Targeting a composition of PSMA<sub>14</sub>-PNMEP<sub>100</sub> at 20% w/w solids, aliquots of the reaction solution were extracted under nitrogen every 5 min for 50 min with <sup>1</sup>H NMR spectroscopy being used to monitor the extent of polymerisation (see Figure S2 in ESI for assigned <sup>1</sup>H NMR spectra). Figure 1 shows the conversion vs. time curve.

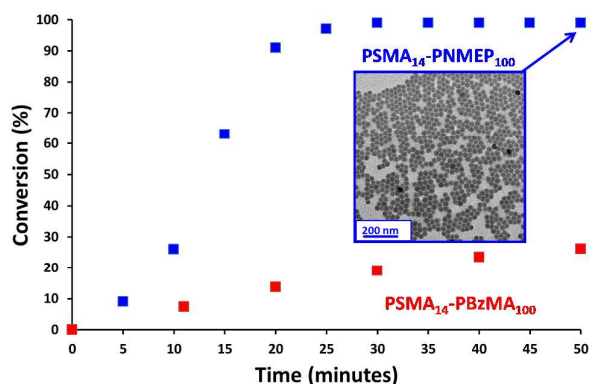

**Figure 1.** Kinetics of the polymerisation of NMEP and BzMA when targeting PSMA<sub>14</sub>-PNMEP<sub>100</sub> (blue) and PSMA<sub>14</sub>-PBzMA<sub>100</sub> (red) at 90 °C at 20% w/w solids. Insert: transmission electron microscopy image obtained after 50 min for PSMA<sub>14</sub>-PNMEP<sub>100</sub> showing the formation of near-monodisperse spherical nanoparticles with a mean diameter of 27 nm.

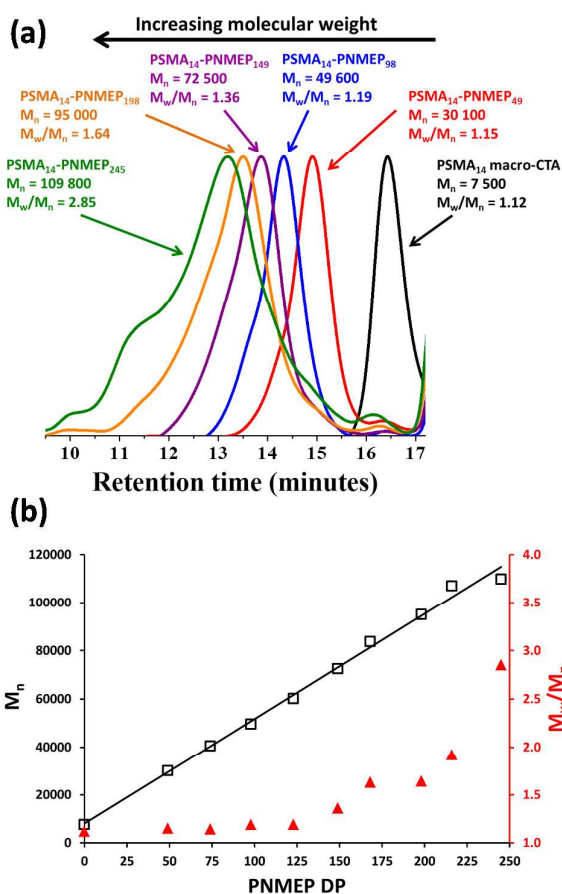

**Figure 2.** (a) 3:1 Chloroform/methanol GPC curves obtained for PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles prepared at 10% w/w solids via RAFT dispersion polymerisation of NMEP at 90 °C. (b) Relationship between target PNMEP DP and GPC  $M_n$  (black axis) and  $M_w/M_n$  (red axis) for the same series of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles prepared at 10% w/w solids.


Approximately 90% conversion was attained within 20 min, with 99 % conversion being achieved within 30 min. This is significantly faster than other RAFT dispersion polymerisations that have been conducted in *n*-alkanes.<sup>13, 31, 33-35</sup> For example, Fielding et al. reported that the polymerisation of benzyl methacrylate at 90 °C in *n*-heptane using a PLMA<sub>17</sub> macro-CTA at 15% solids took 5 h to reach 95% conversion.<sup>33</sup> Moreover, these PLMA-PBzMA diblock copolymers were prepared using a lower macro-CTA/initiator molar ratio of 2.0 compared to the PSMA-PNMEP diblock copolymer synthesis reported in the present study. In view of our unexpected observations, we conducted a kinetic study of the synthesis of PSMA<sub>14</sub>-PBzMA<sub>100</sub> in *n*-dodecane under precisely the same conditions employed for PSMA<sub>14</sub>-PNMEP<sub>100</sub> in order to enable a direct comparison to be made between these two PISA formulations. Both NMEP polymerisations were performed at 90 °C using a macro-CTA/initiator molar ratio of 4.0 at 20% w/w solids. The kinetic data obtained for PSMA<sub>14</sub>-PBzMA<sub>100</sub> are shown in Figure 1. A BzMA conversion of just 19% was achieved within 30 min (although 95% conversion was eventually achieved after 6 h), which indicates a much slower rate of polymerisation than that of NMEP (see Figure S3 in ESI). This is attributed to the highly polar nature of the latter monomer: similar polarity effects for monomers and solvents have been reported in the literature.<sup>39-41</sup> TEM analysis of the diluted PSMA<sub>14</sub>-PNMEP<sub>100</sub> dispersion recorded after 50 min (> 99% conversion) revealed near-monodisperse spherical nanoparticles with a mean diameter of 27 ± 3 nm (Figure 1, inset). GPC analysis of aliquots taken during the kinetic run indicated a monotonic increase in number-average molecular weight with conversion, with a final  $M_n$  of 49,900 and a relatively low final  $M_w/M_n$  of 1.19 (See Figure S4 in ESI).

#### Synthesis of a series of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer spheres via RAFT dispersion polymerisation

Utilising the above kinetic data, a series of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers were prepared at 10% w/w solids. The target degree of polymerisation (DP) for the PNMEP core-forming block (*x*) was systematically varied from 50 to 1000 (see Table 1) and relatively high (> 96%) NMEP conversions were achieved in all cases. PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers with a target PNMEP DP (*x*) of less than 250 were analysed by GPC. Representative chromatograms for *x* = 49, 98, 149, 198 and 245 are shown in Figure 2a. All PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers exhibited high blocking efficiencies relative to the PSMA<sub>14</sub> macro-CTA and the copolymer  $M_n$  increased as higher PNMEP DPs were targeted, as expected. Figure 2b shows the relationship between both  $M_n$  and  $M_w/M_n$  with respect to the actual PNMEP DP, as calculated from the corresponding <sup>1</sup>H NMR conversions assuming 100 % blocking efficiency. A linear increase in  $M_n$  with PNMEP DP is observed, which is characteristic of a pseudo-living polymerisation. However, gradual broadening of the molecular weight distribution is also observed, with  $M_w/M_n$  values reaching as high as 2.85 for PSMA<sub>14</sub>-PNMEP<sub>245</sub>. In principal, this progressive increase in  $M_w/M_n$  when targeting higher PNMEP DPs could be the result of a dimethacrylate impurity in the NMEP monomer, which has a purity of only 96%. However, an alternative explanation could be chain transfer to polymer, with the two methylene carbonyl protons on the pyrrolidone ring being particularly prone to abstraction.<sup>42</sup> Alternatively, the two pairs of azamethylene protons in the NMEP residues may also participate in such a side reaction. When targeting DPs greater than 250, PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers became insoluble in the 3:1 chloroform/methanol eluent and hence could not be analysed by




GPC, suggesting that higher levels of cross-linking lead to a (micro)gel fraction. Fielding et al. also reported relatively high  $M_w/M_n$  values for PLMA-PBzMA PISA formulations when targeting higher PBzMA DPs (PLMA<sub>47</sub>-PBzMA<sub>900</sub>,  $M_w/M_n = 1.76$ ).<sup>33</sup> In contrast, Pei and co-workers obtained low-polydispersity poly(stearyl methacrylate)-poly(3-phenylpropyl methacrylate) (PSMA-PPPMA) diblock copolymers when using a slightly higher macro-CTA/initiator molar ratio of 5.0,<sup>35</sup> although in this earlier study the target DP for the core-forming block was never higher than 165. In the present study,  $M_w/M_n$  values only begin to increase significantly for PSMA<sub>14</sub>-PNMEP<sub>x</sub> when targeting  $x$  values greater than 150 (see Table 1).

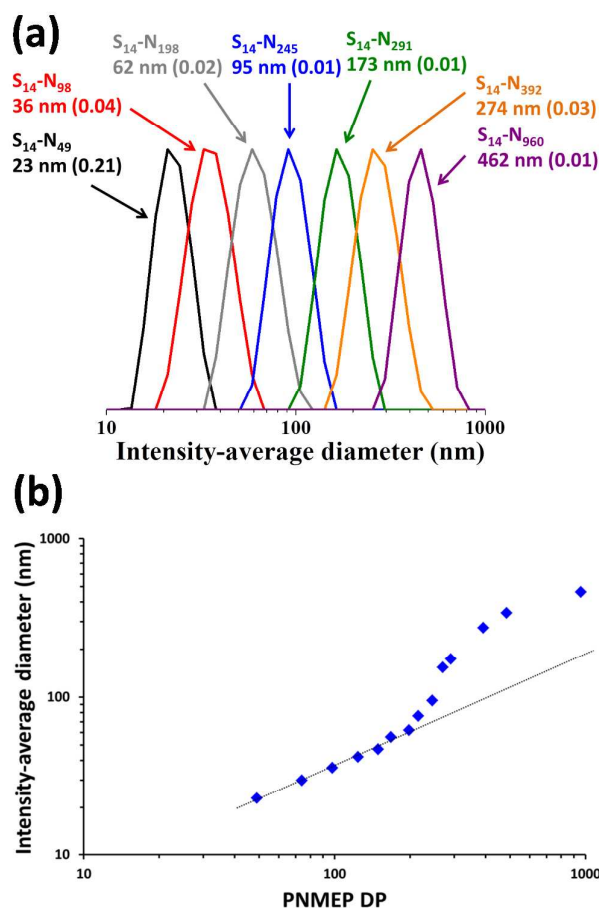

**Figure 3.** (a) DLS intensity-average size distributions for PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles prepared via RAFT dispersion polymerisation of NMEP at 10% w/w solids in *n*-dodecane at 90 °C (N.B. for brevity 'S' denotes PSMA and 'N' denotes PNMEP, the numbers in brackets refer to the DLS polydispersity in each case), (b) a plot of intensity-average diameter vs mean degree of polymerisation of the PNMEP core-forming block. TEM studies confirmed that spherical morphologies were obtained in all cases (see Figure 4).

DLS analysis of these PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles indicated a monotonic increase in the intensity-average diameter when targeting higher PNMEP DPs (Figure 3a). DLS size distributions were relatively narrow in all cases: the smallest nanoparticles (PSMA<sub>14</sub>-PNMEP<sub>49</sub>) were only 23 nm in diameter, while the largest nanoparticles (PSMA<sub>14</sub>-PNMEP<sub>960</sub>) had a

diameter of 462 nm. As far as we are aware, the latter particles are the largest spheres ever reported for PISA syntheses under *any* conditions.<sup>12, 43</sup> The relationship between DLS diameter and core-forming block DP is shown in Figure 3b. There is an initial linear increase in particle size up to a DP of approximately 200, with a non-linear regime thereafter. This complex behaviour is not currently understood and clearly warrants further study.

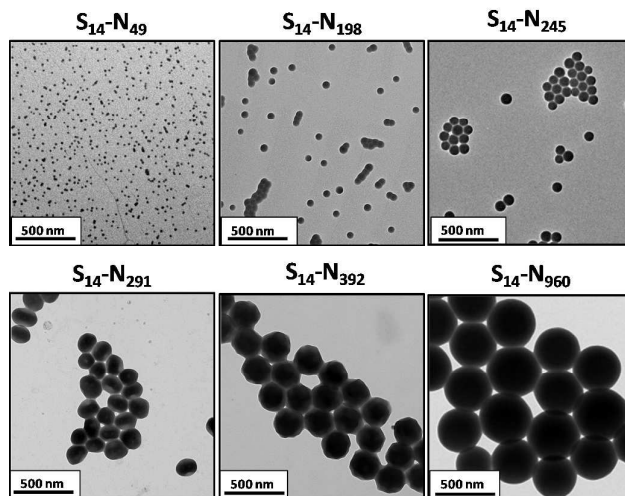


**Figure 4.** TEM images obtained for PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles prepared at 10% w/w solids in *n*-dodecane showing well-defined spherical nanoparticles (N.B. for brevity 'S' denotes PSMA and 'N' denotes PNMEP).

TEM studies of the same series of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles prepared at 10% w/w solids indicated an exclusively spherical morphology, rather than higher order morphologies such as worms or vesicles (see Figure 4). As for the DLS data, a monotonic increase in particle diameter is observed with increasing PNMEP DP. Eisenberg and co-workers have reported that, for post-polymerisation processing of poly(styrene)-poly(acrylic acid) diblock copolymers in dilute solution using a solvent switch, spherical nanoparticles can become kinetically trapped and hence no longer represent the equilibrium morphology.<sup>11, 44</sup> Similar effects have been observed for various PISA syntheses based on RAFT dispersion polymerisation.<sup>23, 27, 33, 45</sup> To examine whether this problem also applied to the current PISA formulation, a new series of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers were synthesised at 20% w/w solids. According to the literature, such higher concentrations are often essential for accessing equilibrium non-spherical morphologies, e.g. worms or vesicles.<sup>45</sup>

#### Construction of a PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer phase diagram

The DP of the stabiliser block is an important parameter when targeting higher order morphologies. This is because a relatively high DP leads to more effective steric stabilisation during PISA, which in turn prevents the 1D sphere-sphere fusion that is the essential first step in the formation of worms.<sup>22, 33</sup> For example, Fielding et al. reported that a PLMA<sub>37</sub> macro-CTA produced exclusively spherical nanoparticles, whereas using a shorter PLMA<sub>17</sub> macro-CTA enabled the synthesis of worm-like micelles and vesicles.<sup>33</sup> On this basis, the PSMA<sub>14</sub> macro-CTA utilised herein was

expected to be sufficiently short to stabilise the full range of morphologies at higher solids.

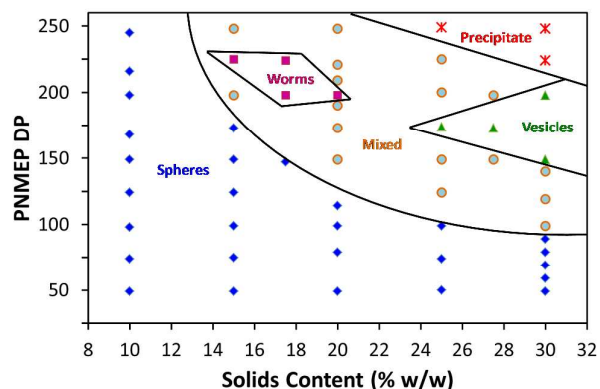


**Figure 5.** Phase diagram for a series of PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers synthesised by RAFT dispersion polymerisation in *n*-dodecane at various concentrations ranging between 10 and 30% w/w. Post-polymerisation analysis of each diblock copolymer dispersion by TEM determined the phase boundaries.

High conversions ( $\geq 95\%$ ) were achieved in all PSMA<sub>14</sub>-PNMEP<sub>x</sub> syntheses conducted at 20% w/w solids (see Table S1). GPC studies indicated an approximately linear increase in  $M_n$  with PNMEP DP between 49 and 248 (see Figure S5 in ESI). Like the GPC data obtained at 10% w/w solids, significantly broader molecular weight distributions were observed when targeting PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers with higher *x* values. TEM analysis confirmed a range of copolymer morphologies; including spherical micelles and worms (see Figure S6 in ESI). However, targeting PNMEP DPs greater than 250 merely led to macroscopic precipitation, hence vesicles could not be accessed under these conditions. A detailed phase diagram was constructed to aid the reproducible targeting of PSMA<sub>14</sub>-PNMEP<sub>x</sub> copolymer morphologies (see Figure 5). In particular, the effect of varying the PNMEP DP between 50 and 250 was examined for PISA syntheses conducted at 10–30% w/w solids. When PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymers were prepared at 10% w/w solids, then a spherical morphology was always obtained, regardless of the *x* value. At 15% w/w solids, spheres were observed for *x* values up to 173, whereas *x* = 90 is the upper limit DP for the sphere phase prepared at 30% w/w solids. These additional observations support the hypothesis that the spheres produced at lower concentrations represent a kinetically-trapped (rather than equilibrium) morphology when targeting higher PNMEP DPs.

A high proportion of the phase space shown in Figure 5 represents mixed phases where two or more morphologies co-exist. The ‘pure’ worm phase is defined as more than 95% of nano-objects analysed by TEM being classified as worms. This highly anisotropic morphology occupies relatively narrow phase space, which is consistent with observations made by Fielding and co-workers for related RAFT dispersion polymerisation syntheses conducted in *n*-alkanes.<sup>13, 33, 34</sup> Both Fielding et al. and Pei et al. have shown that such block copolymer worms form thermo-responsive gels, which undergo reversible degelation on heating via a worm-to-sphere transition.<sup>34–36</sup> Fielding et al. explained this phenomenon in terms of surface plasticisation of the core-forming PBzMA block by the hot *n*-

alkane solvent, since this lowers the effective packing parameter for the block copolymer chains.<sup>34</sup> In contrast, the PSMA<sub>14</sub>-PNMEP<sub>198</sub>

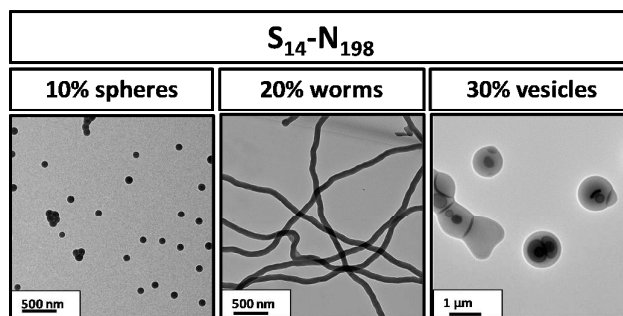

**Figure 6.** TEM images obtained for PSMA<sub>14</sub>-PNMEP<sub>198</sub> diblock copolymer nano-objects prepared at 10, 20 or 30% w/w solids confirming the formation of well-defined spheres, highly anisotropic worms and polydisperse vesicles, respectively (N.B. for brevity ‘S’ denotes PSMA and ‘N’ denotes PNMEP).

worms formed in the present study do *not* exhibit such thermo-responsive behaviour. Presumably, this is simply because *n*-dodecane is always a very poor solvent for the highly polar PNMEP block, even at temperatures of up to 150 °C.


For other PISA formulations reported in the literature<sup>23, 45</sup> vesicles are typically formed at high solids when targeting relatively high core-forming block DPs. However, in the present work vesicles are produced at and above 27.5% w/w solids only when targeting PNMEP DPs of 200 or below. This is because longer core-forming blocks lead to colloiddally unstable dispersions and macroscopic precipitation. Similar observations were made by Warren et al. for a phase diagram constructed for a poly(ethylene glycol)-poly(2-hydroxypropyl methacrylate) PISA formulation.<sup>25</sup> TEM analysis of diluted dispersions of PSMA<sub>14</sub>-PNMEP<sub>2250</sub> nano-objects prepared at or above 25% solids contents confirm the presence of large vesicular aggregates (see Figure S7).

The PSMA<sub>14</sub>-PNMEP<sub>198</sub> composition is particularly interesting, since varying the copolymer concentration yields the full range of morphologies (spheres, worms and vesicles). Thus a near-monodisperse spherical morphology is observed at 10% w/w solids, whereas worms (approximate worm width = 100 nm, but highly polydisperse in worm contour length) are produced at 20% w/w solids and a vesicle phase comprising mainly oligolamellar vesicles<sup>25</sup> is formed at 30% w/w solids (Figure 6). This example nicely illustrates the concentration-dependent morphologies that can be obtained via such PISA syntheses.

#### Pickering emulsifier studies

A 10 g batch of 25 nm diameter PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres were prepared at 10% w/w solids in *n*-dodecane for evaluation as an emulsifier. In principle, homogenisation of these *n*-dodecane nanoparticle dispersions with water could lead to four types of emulsions (Scheme 2). Scenarios 1 and 3 are expected if the nanoparticles are unstable under the homogenisation conditions and break up to form individual diblock copolymer chains that act as a polymeric surfactant. Such *in situ* dissociation has been recently reported by Thompson and co-workers for PGMA-PPHMA spheres in water.<sup>46</sup> Thus, a water-in-oil emulsion is expected if the


hydrophobic PSMA block acts as the stabiliser, as indicated in scenario 1. Alternatively, according to scenario 3, an oil-in-water emulsion should be formed if the (longer) hydrophilic PNMEP acts as the stabiliser. However, based on further studies performed by Thompson et al. using PLMA-PBzMA worms or spheres,<sup>47, 48</sup> the PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres may simply remain intact and stabilise a water-in-oil Pickering emulsion (see scenario 2). Finally, scenario 4 depicts possible inversion of the original hydrophobic PSMA<sub>14</sub>-PNMEP<sub>49</sub> nanoparticles to form hydrophilic PNMEP<sub>49</sub>-PSMA<sub>14</sub> spheres, which could then stabilise an oil-in-water Pickering emulsion.

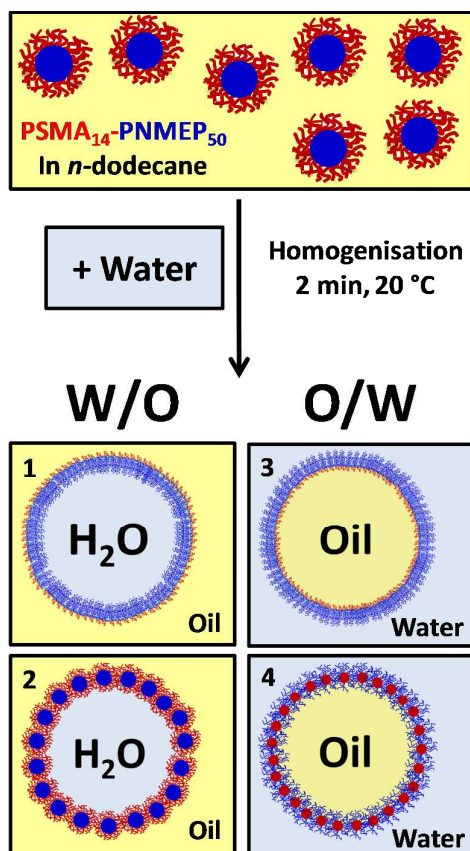

**Scheme 2.** Schematic representation of the four possible types of emulsions which could form as a result of homogenising the PSMA<sub>14</sub>-PNMEP<sub>50</sub> nanoparticles prepared in *n*-dodecane with water. In scenarios 1 and 3, the nanoparticles dissociate to produce amphiphilic diblock copolymer chains that act as a polymeric surfactant stabiliser, producing either water-in-oil or oil-in-water emulsions, respectively. In scenario 2, the hydrophobic nanoparticles are retained intact and adsorb at the oil/water interface to form water-in-oil Pickering emulsions. In scenario 4, morphological inversion to form hydrophilic nanoparticles that stabilise oil-in-water Pickering emulsions.

Initial studies of the effect of shear rate on emulsion formation were performed using a fixed 1.0 % w/w concentration of PSMA<sub>14</sub>-PNMEP<sub>49</sub> nanoparticles. Emulsions were formed by homogenisation of a 50:50 v/v water/*n*-dodecane mixture at 3,500 to 24,000 rpm

for 2 min at 20 °C, with one additional emulsification experiment being conducted via hand-shaking for 2 min. Figure 7a shows digital photographs of the resulting emulsions.

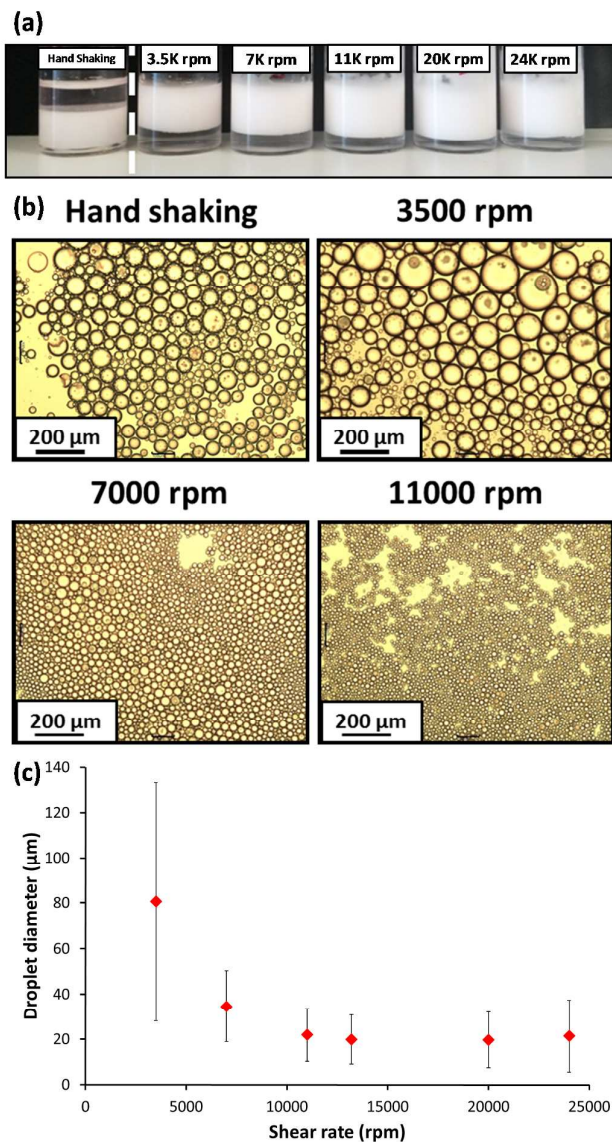


**Figure 7.** (a) Digital photographs obtained for the Pickering emulsions prepared using 1.0% w/w particles at various shear rates. Oil-in-water emulsions are formed in all cases, except when hand-shaking is used; this latter approach results in a water-in-oil emulsion instead. (b) optical microscopy images recorded for the droplets prepared via hand-shaking, or via homogenisation at 3,500 rpm, 7,000 rpm or 11,000 rpm (scale bar = 200 µm), (c) Shear rate dependence for the mean droplet diameter (as determined by laser diffraction) for emulsions prepared using PSMA<sub>14</sub>-PNMEP<sub>50</sub> spherical nanoparticles as the sole emulsifier. The error bars represent the standard deviation of each mean volume-average droplet diameter, rather than the experimental error.

The emulsion formed by hand-shaking resulted in a water-in-oil emulsion as expected, but surprisingly all other emulsions prepared



at higher shear rates resulted in oil-in-water emulsions. However, at this point it was not known whether the PSMA<sub>14</sub>-PNMEP<sub>49</sub> emulsifier was present in the form of nanoparticles or individual copolymer chains.

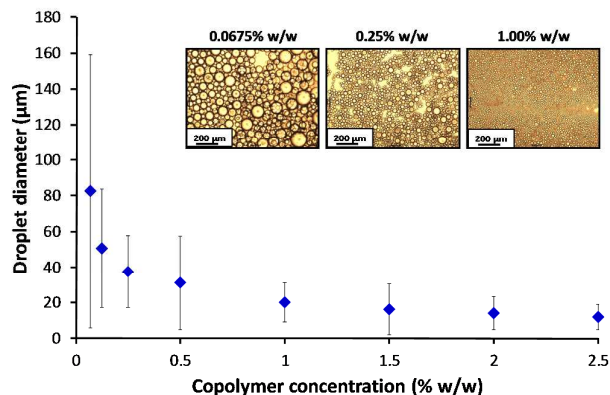

**Figure 8.** Concentration dependence of the mean volume-average droplet diameter (as determined by laser diffraction) for oil-in-water Pickering emulsions prepared at a constant shear rate of 13,200 rpm using PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres. The error bars shown represent the standard deviation of each mean volume-average droplet diameter, rather than the experimental error. Inset: optical microscopy images of the droplets prepared at 0.0675, 0.25 and 1.00% w/w. Scale bar = 200 µm.

All emulsions were imaged by optical microscopy and selected emulsions prepared at various shear rates are shown in Figure 7b. The effect of the shear rate on the mean droplet diameter is evident: larger droplets are formed at 3,500 rpm compared to those produced at either 7,000 rpm or 11,000 rpm. Laser diffraction was utilised to measure the mean diameter of the oil-in-water emulsion droplets (see Figure 7c). A gradual reduction in mean droplet diameter with increasing shear rate was observed: ~80 µm droplets were formed at 3,500 rpm, whereas ~20 µm droplets were obtained at shear rates above 11,000 rpm. Thompson and co-workers reported similar observations for water droplets stabilised by PLMA-PBzMA worms prepared in *n*-dodecane.<sup>47</sup>

DLS studies were undertaken to investigate the effect of the high shear emulsification conditions on the stability of the PSMA<sub>14</sub>-PNMEP<sub>49</sub> nanoparticles. Prior to homogenisation, colloidally stable low-polydispersity nanoparticles with an intensity-average diameter of 25 nm were observed (Figure S8a in ESI). After homogenisation of a 1.0% w/w nanoparticle dispersion in *n*-dodecane (i.e. in the absence of any added water) at 13,200 rpm for 2 min, highly polydisperse particles of 732 nm diameter were obtained. Moreover, the count rate was reduced by a factor of more than three, from 2111 kcps to 604 kcps. This suggests that the spherical nanoparticles are unstable when subjected to high shear and undergo (at least partial) dissociation. In principle, this could potentially result in scenario 3 (Scheme 2) in which the highly amphiphilic diblock copolymer chains may act as a polymeric surfactant. To examine this hypothesis, the copolymer concentration of PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres was varied from 0.0675% w/w to 2.50% w/w and homogenised with an equal volume of water at a fixed shear rate of 13,200 rpm to produce a series of oil-in-water emulsions. The emulsion droplet size distributions were analysed by laser diffraction, see Figure 8.

Clearly, there is a strong concentration dependence: droplets of more than 50 µm are formed at low PSMA<sub>14</sub>-PNMEP<sub>49</sub> concentrations whereas approximately 10 µm droplets are obtained at the highest copolymer concentration. These observations are consistent with the corresponding optical microscopy images (Figure 8, see inset). This indicates that the copolymer actually absorbs in the form of nanoparticles, rather than individual chains. This interpretation is supported by TEM studies, which confirm the presence of spherical particles adsorbed onto a dried emulsion droplet (see Figure S9 in the ESI). Moreover, since oil-in-water emulsions are obtained rather than water-in-oil emulsions, this suggests that *in situ* inversion of the initial hydrophobic PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres to form hydrophilic PNMEP<sub>49</sub>-PSMA<sub>14</sub> spheres occurs, see scenario 4 in Scheme 2. This result was completely unexpected and warrants further investigation.

To further analyse the water-in-oil emulsion system obtained by hand-shaking, a series of such emulsions were prepared by hand-shaking with equal volumes of water using copolymer concentrations of 0.125% to 1.50% w/w. In each case, water-in-oil emulsions were obtained, as judged by optical microscopy (see ESI, Figure S10). These images suggest some concentration dependence for the mean droplet diameter but unfortunately these water-in-oil emulsions proved to be insufficiently stable to enable laser diffraction analysis. Instead, mean droplet diameters were estimated by sizing a minimum of 100 droplets per emulsion (see ESI, Figure S11). As expected, a concentration-dependent mean droplet diameter was observed, which suggests that nanoparticles, rather than copolymer chains, are adsorbed at the oil/water interface when homogenisation is performed at very low shear rates (i.e. hand-shaking). DLS analysis of the *n*-dodecane supernatant after sedimentation of the relatively dense water droplets supported this interpretation. An intensity-average diameter of 28 nm (polydispersity = 0.03) was observed (see ESI, Figure S8b), which is very similar to that of the original nanoparticles (intensity-average diameter = 25 nm; polydispersity = 0.07). These observations, taken together with the concentration-dependent droplet size indicated by optical microscopy studies, suggests that PSMA<sub>14</sub>-PNMEP<sub>49</sub> spherical nanoparticles stabilise water-in-oil Pickering emulsions, see scenario 2 in Scheme 2.

Finally, the effect of varying the volume fraction of the aqueous phase was studied. Three Pickering emulsions were prepared using 0.50% w/w PSMA<sub>14</sub>-PNMEP<sub>49</sub> nanoparticles utilising 25%, 50% or 75% water relative to the volume of nanoparticle dispersion in *n*-dodecane, with homogenisation being conducted at a constant shear rate of 13,200 rpm. Using 75% or 50% water resulted in an oil-in-water emulsion. However, using a water volume fraction of 25% led to the formation of a water-in-oil emulsion. Digital photographs of these three emulsions and their corresponding optical microscopy images are shown in Figure S12. These observations indicate that PSMA<sub>14</sub>-PNMEP<sub>49</sub> spherical nanoparticles enable the preparation of water-in-oil emulsions via two methods: either using very low shear (hand-shaking) or by using a 25% water/75% *n*-dodecane formulation that prevents nanoparticle inversion.

## Conclusions

The RAFT dispersion polymerisation of a highly polar monomer, NMEP, has been conducted in *n*-dodecane using a PSMA<sub>14</sub> macro-CTA to produce a series of diblock copolymer nanoparticles via

PISA. In all cases, high conversions ( $\geq 95\%$ ) were achieved within 2 h at 90 °C. Kinetic studies for a PSMA<sub>14</sub>-PNMEP<sub>100</sub> formulation indicated more than 99% conversion within 50 min, which is much faster than the rate of polymerisation of a non-polar monomer (benzyl methacrylate) under precisely the same conditions. GPC analysis confirmed a linear evolution in  $M_n$  when targeting higher PNMEP DPs, as expected. However, significantly broader molecular weight distributions ( $M_w/M_n > 1.50$ ) were observed when targeting PNMEP DPs above approximately 150. This is attributed to either a dimethacrylate impurity in the NMEP monomer or perhaps chain transfer to PNMEP. TEM analysis of the PSMA<sub>14</sub>-PNMEP<sub>x</sub> diblock copolymer nanoparticles prepared at 10% w/w solids indicated an exclusively spherical morphology. Both DLS and TEM studies indicated that remarkably large uniform spheres of 462 nm diameter could be obtained when targeting  $x = 1000$ . As far as we are aware, these are the largest spheres ever reported for PISA formulations. Conducting PISA syntheses at either 15.0 or 17.5% w/w solids enabled PSMA<sub>14</sub>-PNMEP<sub>198</sub> worms to be obtained. These worms formed free-standing gels, but do not appear to exhibit thermo-responsive behaviour. Construction of a phase diagram enabled reproducible targeting of pure spherical micelles, worms or vesicles. PSMA<sub>14</sub>-PNMEP<sub>49</sub> spheres were evaluated as putative Pickering emulsifiers. Water-in-oil emulsions were obtained in hand-shaking (low shear) experiments, as expected for such hydrophobic particles. However, oil-in-water emulsions were unexpectedly obtained when emulsification was conducted under high shear. This is attributed to *in situ* inversion to produce hydrophilic PNMEP<sub>49</sub>-PSMA<sub>14</sub> spheres. Thus the same diblock copolymer spheres can form two types of Pickering emulsion depending on the emulsification conditions.

## Acknowledgements

EPSRC is thanked for funding a DTA PhD studentship and also for a Programme Grant (EP/I012060/1). Ashland Specialty Ingredients (Bridgewater, NJ) is thanked for CASE support of this PhD project, supplying the NMEP monomer and for permission to publish this work.

## Notes and references

- 1 S. Newman, *Journal of Applied Polymer Science*, 1962, **6**, S15-S16.
- 2 S. Krause, *The Journal of Physical Chemistry*, 1964, **68**, 1948-1955.
- 3 Z. Tuzar and P. Kratochvil, *Advances in Colloid and Interface Science*, 1976, **6**, 201-232.
- 4 M. Moffitt, H. Vali and A. Eisenberg, *Chemistry of Materials*, 1998, **10**, 1021-1028.
- 5 Y.-Y. Won, H. T. Davis and F. S. Bates, *Science*, 1999, **283**, 960-963.
- 6 P. Dalhaimer, A. J. Engler, R. Parthasarathy and D. E. Discher, *Biomacromolecules*, 2004, **5**, 1714-1719.
- 7 D. E. Discher and A. Eisenberg, *Science*, 2002, **297**, 967-973.
- 8 Y. Li and S. P. Armes, *Angew. Chem. Int. Ed.*, 2010, **49**, 4042-4046.
- 9 B. Charleux, G. Delaittre, J. Rieger and F. D'Agosto, *Macromolecules*, 2012, **45**, 6753-6765.
- 10 N. J. Warren and S. P. Armes, *Journal of the American Chemical Society*, 2014, **136**, 10174-10185.
- 11 L. Zhang and A. Eisenberg, *Polymers for Advanced Technologies*, 1998, **9**, 677-699.
- 12 V. J. Cunningham, A. M. Alswieleh, K. L. Thompson, M. Williams, G. J. Leggett, S. P. Armes and O. M. Musa, *Macromolecules*, 2014, **47**, 5613-5623.
- 13 M. J. Derry, L. A. Fielding and S. P. Armes, *Polymer Chemistry*, 2015, **6**, 3054-3062.
- 14 J.-S. Wang and K. Matyjaszewski, *Journal of the American Chemical Society*, 1995, **117**, 5614-5615.
- 15 K. Matyjaszewski, *Macromolecules*, 2012, **45**, 4015-4039.
- 16 J. Chiefari, Y. K. Chong, F. Ercole, J. Krstina, J. Jeffery, T. P. T. Le, R. T. A. Mayadunne, G. F. Meijs, C. L. Moad, G. Moad, E. Rizzardo and S. H. Thang, *Macromolecules*, 1998, **31**, 5559-5562.
- 17 G. Moad, E. Rizzardo and S. H. Thang, *Australian Journal of Chemistry*, 2005, **58**, 379-410.
- 18 G. Moad, E. Rizzardo and S. H. Thang, *Aust. J. Chem.*, 2006, **59**, 669-692.
- 19 G. Moad, E. Rizzardo and S. H. Thang, *Australian Journal of Chemistry*, 2009, **62**, 1402-1472.
- 20 B. Charleux, F. D'Agosto and G. Delaittre, *Advances in Polymer Science*, 2010, **233**, 125-183.
- 21 P. B. Zetterlund, S. C. Thickett, S. Perrier, E. Bourgeat-Lami and M. Lansalot, *Chemical Reviews*, 2015, **115**, 9745-9800.
- 22 A. Blanazs, J. Madsen, G. Battaglia, A. J. Ryan and S. P. Armes, *J. Am. Chem. Soc.*, 2011, **133**, 16581-16587.
- 23 S. Sugihara, A. Blanazs, S. P. Armes, A. J. Ryan and A. L. Lewis, *J. Am. Chem. Soc.*, 2011, **133**, 15707-15713.
- 24 A. Blanazs, R. Verber, O. O. Mykhaylyk, A. J. Ryan, J. Z. Heath, C. W. I. Douglas and S. P. Armes, *J. Am. Chem. Soc.*, 2012, **134**, 9741-9748.
- 25 N. J. Warren, O. O. Mykhaylyk, D. Mahmood, A. J. Ryan and S. P. Armes, *J. Am. Chem. Soc.*, 2014, **136**, 1023-1033.
- 26 E. R. Jones, M. Semsarilar, A. Blanazs and S. P. Armes, *Macromolecules*, 2012, **45**, 5091-5098.
- 27 M. Semsarilar, E. R. Jones, A. Blanazs and S. P. Armes, *Advanced Materials*, 2012.
- 28 D. Zehm, L. P. D. Ratcliffe and S. P. Armes, *Macromolecules*, 2013, **46**, 128-139.
- 29 Y. Pei and A. B. Lowe, *Polymer Chemistry*, 2014, **5**, 2342-2351.
- 30 L. Houillot, C. Bui, M. Save, B. Charleux, C. Farcet, C. Moire, J.-A. Raust and I. Rodriguez, *Macromolecules*, 2007, **40**, 6500-6509.
- 31 L. Houillot, C. Bui, C. Farcet, C. Moire, J.-A. Raust, H. Pasch, M. Save and B. Charleux, *ACS Appl. Mater. Interfaces*, 2010, **2**, 434-442.
- 32 J.-A. Raust, L. Houillot, M. Save, B. Charleux, C. Moire, C. Farcet and H. Pasch, *Macromolecules*, 2010, **43**, 8755-8765.

## ARTICLE


## Journal Name

- 33 L. A. Fielding, M. J. Derry, V. Ladmiral, J. Rosselgong, A. M. Rodrigues, L. P. Ratcliffe, S. Sugihara and S. P. Armes, *Chemical Science*, 2013, **4**, 2081-2087.
- 34 L. A. Fielding, J. A. Lane, M. J. Derry, O. O. Mykhaylyk and S. P. Armes, *Journal of the American Chemical Society*, 2014, **136**, 5790-5798.
- 35 Y. Pei, L. Thurairajah, O. R. Sugita and A. B. Lowe, *Macromolecules*, 2015, **48**, 236-244.
- 36 Y. Pei, O. R. Sugita, L. Thurairajah and A. B. Lowe, *RSC Advances*, 2015, **5**, 17636-17646.
- 37 Q. Zhang and S. Zhu, *ACS Macro Letters*, 2015, **4**, 755-758.
- 38 J. N. Israelachvili, D. J. Mitchell and B. W. Ninham, *J. Chem. Soc., Faraday Trans. 2*, 1976, **72**, 1525-1568.
- 39 K. Matyjaszewski, Y. Nakagawa and C. B. Jasieczek, *Macromolecules*, 1998, **31**, 1535-1541.
- 40 E. J. Lobb, I. Ma, N. C. Billingham, S. P. Armes and A. L. Lewis, *Journal of the American Chemical Society*, 2001, **123**, 7913-7914.
- 41 S. Beuermann and M. Buback, *Progress in Polymer Science*, 2002, **27**, 191-254.
- 42 F. Haaf, A. Sanner and F. Straub, *Polymer Journal*, 1985, **17**, 143-152.
- 43 N. P. Truong, M. V. Dussert, M. R. Whittaker, J. F. Quinn and T. P. Davis, *Polymer Chemistry*, 2015, **6**, 3865-3874.
- 44 Y. Mai and A. Eisenberg, *Chemical Society Reviews*, 2012, **41**, 5969-5985.
- 45 A. Blanazs, A. J. Ryan and S. P. Armes, *Macromolecules*, 2012, **45**, 5099-5107.
- 46 K. Thompson, C. Mable, A. Cockram, N. Warren, V. Cunningham, E. Jones, R. Verber and S. Armes, *Soft Matter*, 2014, **10**, 8615-8626.
- 47 K. L. Thompson, C. J. Mable, J. A. Lane, M. J. Derry, L. A. Fielding and S. P. Armes, *Langmuir*, 2015, **31**, 4137-4144.
- 48 K. Thompson, L. Fielding, O. Mykhaylyk, J. Lane, M. Derry and S. Armes, *Chemical Science*, 2015, **6**, 4207-4214.

**Synthesis, characterisation and Pickering emulsifier performance of poly(stearyl methacrylate)-poly(*N*-2-(methacryloyloxy)ethyl pyrrolidone) diblock copolymer nano-objects via RAFT dispersion polymerisation in *n*-dodecane**

V. J. Cunningham, S. P. Armes\*, and O. M. Musa

**TOC Graphic**

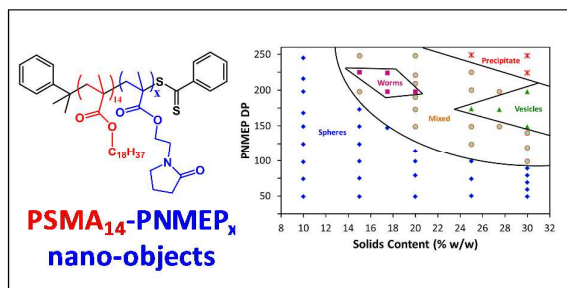

**Summary Text.** Block copolymer spheres, worms or vesicles can be prepared via RAFT dispersion polymerisation of *N*-(methacryloyloxy)ethyl pyrrolidone in *n*-dodecane using a poly(stearyl methacrylate) chain transfer agent