

# Chemical Science

www.rsc.org/chemicalscience



ISSN 2041-6539



ROYAL SOCIETY  
OF CHEMISTRY

EDGE ARTICLE

Jinlong Gong *et al.*

Spatial separation of oxidation and reduction co-catalysts for efficient charge separation: Pt@TiO<sub>2</sub>@MnO<sub>x</sub> hollow spheres for photocatalytic reactions

175  
YEARS



CrossMark  
click for updatesCite this: *Chem. Sci.*, 2016, 7, 890

# Spatial separation of oxidation and reduction cocatalysts for efficient charge separation: Pt@TiO<sub>2</sub>@MnO<sub>x</sub> hollow spheres for photocatalytic reactions†

Ang Li, Tuo Wang, Xiaoxia Chang, Weiting Cai, Peng Zhang, Jijie Zhang and Jinlong Gong\*

Efficient charge separation is a critical factor for solar energy conversion by heterogeneous photocatalysts. This paper describes the complete spatial separation of oxidation and reduction cocatalysts to enhance the efficacy of charge separation and surface reaction. Specifically, we design Pt@TiO<sub>2</sub>@MnO<sub>x</sub> hollow spheres (PTM-HSs) with Pt and MnO<sub>x</sub> loaded onto the inner and outer surface of TiO<sub>2</sub> shells, respectively. Pt favours electron trapping, while MnO<sub>x</sub> tends to collect holes. Upon generation from TiO<sub>2</sub>, electrons and holes flow inward and outward of the spherical photocatalyst, accumulating on the corresponding cocatalysts, and then take part in redox reactions. Combined with other advantages, such as the large surface area and appropriate pore size, the PTM-HSs exhibit high efficiency for the photocatalytic oxidation of water and benzyl alcohol. The mechanism of the oxidation process of benzyl alcohol over the photocatalyst is also presented.

Received 3rd November 2015  
Accepted 26th November 2015

DOI: 10.1039/c5sc04163e

www.rsc.org/chemicalscience

## Introduction

Efficient charge separation is a critical factor for solar energy conversion by semiconductor-based systems. It is crucial for increasing the performance of solar cells, photoelectrochemical and photocatalytic systems.<sup>1,2</sup> As an important application, photocatalytic oxidation requires exceptionally efficient charge separation. Within photooxidation reactions, the photooxidation of water into O<sub>2</sub> has long been considered as the bottleneck of the water-splitting process, so the invention of highly active water oxidation catalysts is a key step in the development of light-driven water splitting.<sup>3</sup> In addition, the photocatalytic oxidation system can also be used to produce highly valued chemicals such as aldehydes and ketones. Compared with traditional methods with high temperature, toxic oxidants and hazardous waste,<sup>4</sup> photocatalytic oxidation processes can be performed under mild and environmentally friendly conditions. Substances unstable at high temperatures may also be synthesized by such selective light-assisted processes.<sup>4</sup> Recently, the emergence of a new family of metal-free polymer photocatalysts provided fine methods to enhance charge separation.<sup>5,6</sup> For instance, heterojunctions between carbon nitride

and sulfur-mediated carbon nitride have been constructed to promote photocatalytic reactions.<sup>6</sup> Besides, many other strategies were adopted to improve charge separation, while the results remain unsatisfactory because of diverse problems.<sup>1,7–9</sup>

Cocatalyst loading has been proved to be an effective approach to accelerate charge separation.<sup>1</sup> Cocatalysts can be designed for oxidation and reduction purposes. Oxidation cocatalysts tend to capture holes (PbO<sub>2</sub>, MnO<sub>x</sub> and PdS,<sup>10</sup> *etc.*), while reduction cocatalysts prefer electrons (Pt, Pd,<sup>1</sup> *etc.*). Meanwhile, they can promote the surface reaction of the redox process.<sup>11</sup> Yu *et al.* have reported the fabrication of TiO<sub>2</sub> nanosheets loaded with Pt. Compared with pure TiO<sub>2</sub> nanosheets, the photocatalytic activity of Pt decorated nanosheets was obviously improved.<sup>2</sup>

Simultaneous loading of oxidation and reduction cocatalysts could further improve the photocatalytic activity. Colón *et al.* fabricated Pt–TiO<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>–MnO<sub>x</sub> composites and successfully proved that Pt and MnO<sub>x</sub> trap electrons and holes, respectively, leading to a further separation of charges.<sup>12</sup> However, both reduction and oxidation cocatalysts are randomly distributed in this case, which results in a random flow direction of charge carriers when they migrate to the cocatalysts. In such a scenario, the possibility of electron–hole recombination will be increased. In addition, the short distance between the reduction and oxidation cocatalysts is unfavorable for redox reactions, for close redox sites may lead to severe back-reactions.

Spatial separation of oxidation and reduction cocatalysts is a method to solve this problem, yet limited success has been

Key Laboratory for Green Chemical Technology of Ministry of Education, School of Chemical Engineering and Technology, Collaborative Innovation Center of Chemical Science and Engineering, Tianjin University, Weijin Road 92, Tianjin, 300072, P. R. China. E-mail: jlgong@tju.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c5sc04163e



reported. Carbon nitride nanosheets have been fabricated to separate different cocatalysts, promoting the locally-incompatible oxidation and reduction reactions on the two surfaces.<sup>5</sup> In addition, Pt particles (reduction cocatalyst) and  $\text{MnO}_x$  particles (oxidation cocatalyst) have been nicely deposited on different facets of  $\text{BiVO}_4$ , exhibiting increased performance when compared to the randomly deposited counterparts.<sup>1</sup> To achieve more complete spatial separation of oxidation and reduction cocatalysts, as well as to make full use of the photocatalyst, we design and synthesize  $\text{Pt@TiO}_2\text{@MnO}_x$  hollow spheres (PTM-HSs) with Pt particles and  $\text{MnO}_x$  loaded onto the inner and outer surfaces of  $\text{TiO}_2$  hollow spheres, respectively. Different cocatalysts can be completely separated by the  $\text{TiO}_2$  shells without intermixing. The photocatalytic material can be fully used owing to the thin shell (about 40–60 nm) of  $\text{TiO}_2$  hollow spheres.  $\text{TiO}_2$  is chosen in this study since it serves as an excellent benchmark photocatalyst for comparison purposes.<sup>13–15</sup> Additionally, as a model structure, this concept (*i.e.*, different cocatalysts are separated by  $\text{TiO}_2$  shells completely) can be extended to other redox cocatalysts such as Au, Ag,  $\text{PbO}_2$ , *etc.*<sup>1</sup>

Upon generation from  $\text{TiO}_2$ , electrons and holes will flow inward and outward of the spherical  $\text{TiO}_2$  shells, respectively, accumulating on corresponding cocatalysts and then taking part in redox reactions (Fig. 1). Electrons can promote the photo-reduction, while holes participate in the photo-oxidation.<sup>16</sup> Thus, the oxidation of benzyl alcohol accompanied by the elimination of electrons by  $\text{O}_2$  is described in Fig. 1a. The reduction and oxidation reactions take place at different sides of the  $\text{TiO}_2$  shells, which is critical for effective charge separation. In addition, light will pass through the thin  $\text{TiO}_2$  shell and keep reflecting in the cavity, increasing the scattering length for enhanced light-absorption. Combined with the large surface area, the PTM-HSs exhibit high efficiency for the photocatalytic oxidation of benzyl alcohol, a representative alcohol containing phenyl groups. Generally, the appropriate catalysts for benzyl alcohol oxidation can also perform well in the oxidation of other similar chemicals.<sup>17</sup> Thus, the current photoredox catalysis system can be expanded for other relevant organic synthesis of fine chemicals. Additionally, we propose a two-step

photooxidation mechanism for PTM-HSs, which may provide inspiration for the design of similar catalysts with high activity.

## Results and discussion

The synthesis of PTM-HSs (Fig. 2) starts from  $\text{SiO}_2$  nanospheres prepared by a modified Stöber method, with  $\text{H}_2\text{PtCl}_6$  adsorbed on the surface of  $\text{SiO}_2$ .<sup>18</sup> Then they were calcined at 500 °C for 2 hours (h) under  $\text{H}_2$  atmosphere to form Pt particles anchored on  $\text{SiO}_2$  (Fig. 2a and f). Subsequent coating of an amorphous  $\text{TiO}_2$  shell was performed by the hydrolysis of titanium *tert*-butoxide (TBOT) (Fig. 2b and g). Then the samples were calcined to improve the crystallinity of  $\text{TiO}_2$ . It should be noted that direct calcination would destroy the structure of the  $\text{TiO}_2$  shells (Fig. S2†). To preserve the morphology, another layer of  $\text{SiO}_2$  was added as a coating to form the outermost protective layer (Fig. 2c and h). After calcination, the outer and inner silica layers were removed by  $\text{NaOH}$  (1.67 M) etching at 70 °C for 8 h to form  $\text{Pt@TiO}_2$  hollow spheres (PT-HSs) (Fig. 2d and i). Finally,  $\text{MnO}_x$  was selectively deposited on the outer surface of PT-HSs to form PTM-HSs (Fig. 2e and j and S3†) by a photo-deposition method (Fig. S1†).

The successful synthesis of the PT-HSs is further validated. Fig. 3a shows that most Pt particles with an average size of  $ca.$   $3.2 \pm 1.3$  nm (Fig. 3c) are uniformly loaded onto the inner surface of  $\text{TiO}_2$  shells. A few Pt particles agglomerate to form larger ones. The high resolution transmission electron microscopy (HRTEM) image of the area near the inner surface of  $\text{TiO}_2$  shells (Fig. 3b) shows that the lattice spacing of 0.2227 nm and 0.3520 nm match well with the (111) planes of Pt and the (101) planes of anatase. It can be seen that a hexagonal Pt particle is coated by a layer of  $\text{TiO}_2$  (Fig. 3b), resulting from the strong interaction between Pt and  $\text{TiO}_2$ . A STEM-energy-dispersive X-ray spectroscopy (EDS) line scan was performed through the center of an individual PT-HS particle (inset in Fig. 3d and e), which further confirms the position of Pt particles relative to the  $\text{TiO}_2$  shell. Fig. 3d shows strong signals of Ti and O at the edge of the PT-HS, which reveals a typical structure of  $\text{TiO}_2$  hollow spheres. The  $\text{TiO}_2$  shell is marked in Fig. 3d by

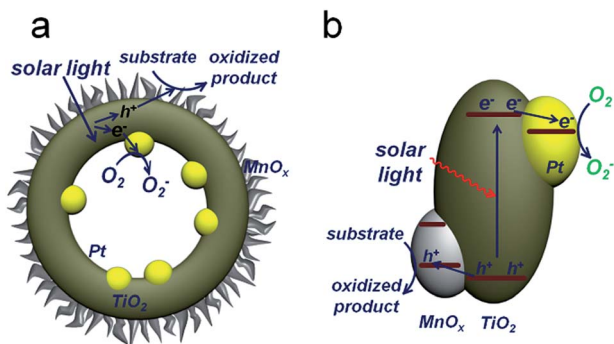


Fig. 1 Proposed mechanism for photocatalytic oxidation by PTM-HSs. Pt and  $\text{MnO}_x$  are spatially separated by  $\text{TiO}_2$ . (a) The reaction process. (b) Band structure of the catalyst.

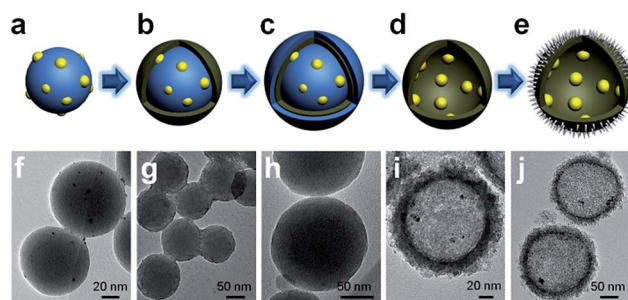


Fig. 2 Schematic illustration and TEM images of the formation process of PTM-HSs. (a) and (f) Pt loaded onto  $\text{SiO}_2$  nanospheres to form  $\text{SiO}_2\text{-Pt}$ . (b) and (g)  $\text{TiO}_2$  layers were coated on  $\text{SiO}_2\text{-Pt}$  to form  $\text{SiO}_2\text{-Pt@TiO}_2$ . (c) and (h)  $\text{SiO}_2$  protective layers were coated on  $\text{SiO}_2\text{-Pt@TiO}_2$  to form  $\text{SiO}_2\text{-Pt@TiO}_2\text{@SiO}_2$ . (d) and (i) PT-HSs. (e) and (j) PTM-HSs. The outermost spine-like layer in image (j) is the  $\text{MnO}_x$  layer.



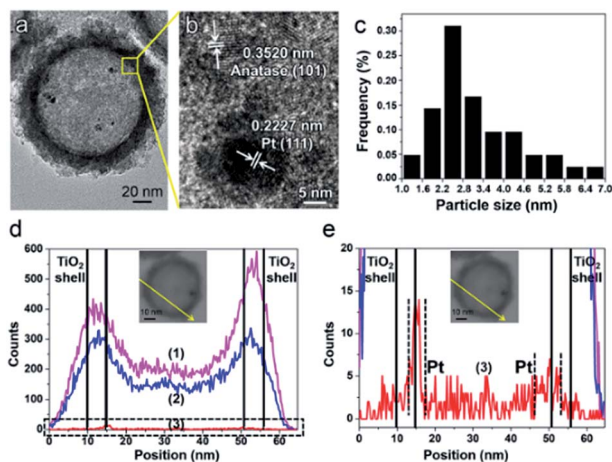


Fig. 3 The confirmation of PT-HS structures. (a) TEM image of a PT-HS. (b) HRTEM image of the area near the inner surface of the  $\text{TiO}_2$  shell. (c) The distribution of the particle size. (d) EDS line scan of a PT-HS. The part in the dotted pane is magnified in image (e). (e) The magnified patterns of the EDS line scan. Inset in image (d) and (e): the path of the EDS line scan. Curves (1), (2) and (3) in image (d) and (e) refer to the signals of Ti, O and Pt, respectively.

two groups of vertical lines, indicating the wall of the  $\text{TiO}_2$  shell based on Ti and O signals in the EDS line scan. Fig. 3e shows the magnified Pt EDS signal, demonstrating that Pt particles are loaded onto the inner surface of the  $\text{TiO}_2$  shell. It is not possible to use an EDS area scan to perform such confirmation because of the low loading of Pt (1%, measured by ICP) (Fig. S4d†).

The structure of the PTM-HSs is confirmed by the same method (Fig. 4), where  $\text{MnO}_x$  is identified on the outer surface of  $\text{TiO}_2$  shells. The universal existence of PTM-HSs can be demonstrated by the TEM image of a larger area (Fig. S3†).

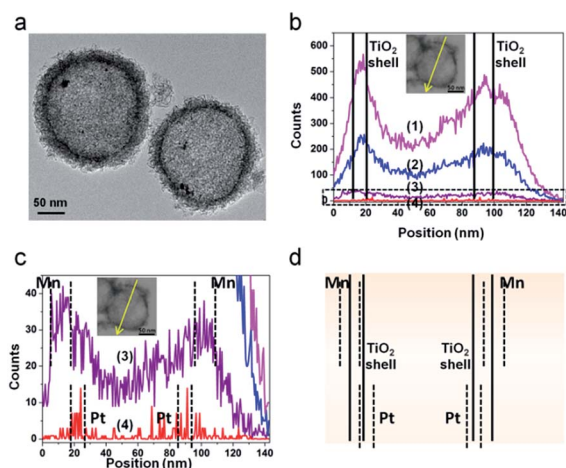


Fig. 4 The confirmation of PTM-HS structures. (a) TEM image of PTM-HSs. (b) EDS line scan of a PTM-HS. The part in the dotted pane is magnified in image c. (c) The magnified patterns of the EDS line scan. (d) The relative positions of Mn, Pt and the  $\text{TiO}_2$  shell. Inset in (b) and (c): the path of the EDS line scan. Curves (1), (2), (3) and (4) in images (b) and (c) refer to the signals of Ti, O, Mn and Pt, respectively.

The pore size and Brunauer–Emmett–Teller (BET) surface area of PTM-HSs are measured by  $\text{N}_2$  adsorption, and determined to be 5.0 nm (average pore size) and  $298 \text{ m}^2 \text{ g}^{-1}$ , respectively (Fig. S5a†). The results indicate a mesoporous structure, which is the prerequisite for effective immigration of reactants. Additionally, X-ray diffraction (XRD, Fig. S5b†) and HRTEM of the spine-like layer (Fig. S5c and d†) prove that the PTM-HSs consist of Pt, anatase and  $\text{MnO}_x$ , where  $x$  is between 1.0 and 2.0. Highly crystallized anatase instead of a rutile shell is formed, which is capable of achieving higher photocatalytic activity.<sup>19,20</sup> The components of the catalysts can be further confirmed by X-ray photoelectron spectroscopy (XPS, Fig. S8†).

For comparison, reference catalysts such as pure  $\text{TiO}_2$  hollow spheres (T-HSs) (Fig. S6a and b†) and  $\text{TiO}_2/\text{Pt}/\text{MnO}_x$  hollow spheres (T/P/M-HSs) (Fig. S6c–f†) were synthesized by a similar method. PT-HSs were also used as reference catalysts. T/P/M-HSs were synthesized by impregnating T-HSs in solutions of  $\text{H}_2\text{PtCl}_6$  and  $\text{MnSO}_4$  in sequence to form a structure in which the Pt particles and  $\text{MnO}_x$  distributed randomly on both the inner and outer surfaces.

Catalysts containing Pt and  $\text{TiO}_2$  can exhibit activity in the photooxidation of alcohols (details are discussed in Fig. S12†) and water (Fig. 5a) under visible light, because of the surface plasmonic resonance effect (SPR) of Pt (Fig. S12e†).<sup>17,21,22</sup> As shown in Fig. 5a, the highest water oxidation activity is achieved for the PTM-HSs. The deposited Pt on the inner surface can collect electrons to reduce  $\text{IO}_3^-$  ions, and the  $\text{MnO}_x$  photo-deposited selectively on the outer surface can accumulate holes for water oxidation. For PT-HSs, although the amounts of loaded species and the topography of the catalysts are similar, the promotion effect of the cocatalysts is not as evident as that of PTM-HSs, indicating that the photocatalytic performance can

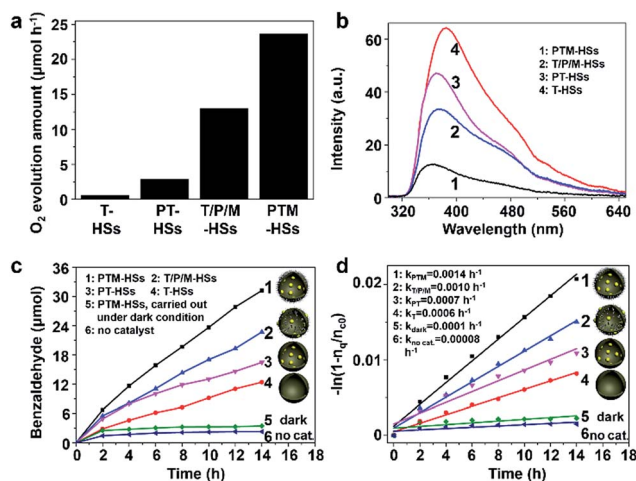


Fig. 5 (a) The activity for photocatalytic water oxidation under visible light ( $\lambda > 420 \text{ nm}$ ). 0.03 g of catalyst was used. (b) The PL spectra (excited at  $\lambda = 235 \text{ nm}$ ) of diverse catalysts. (c) The activity for photocatalytic alcohol oxidation under UV light. (d) The corresponding kinetic rate plots. Traces 1–6 refer to PTM-HSs, T/P/M-HSs, PT-HSs, T-HSs, PTM-HSs under dark conditions, and no catalyst, respectively. Traces 1–4 and trace 6 are carried out under UV irradiation. 0.03 g of catalyst was used.





be greatly enhanced when the reduction/oxidation cocatalysts are spatially separated. The activity of T-HSs and PT-HSs is even lower. These results can be explained by the improvement of the charge separation, which can be demonstrated by the photoluminescence (PL) spectra (Fig. 5b). The emission intensity of T-HSs is the strongest, resulting from the severe recombination of photogenerated charges. In contrast, the intensity of PT-HSs, T/P/M-HSs and PTM-HSs are reduced by about 25%, 45% and 80%, respectively, indicating an enhanced suppression of the recombination process.

To illustrate that the enhancement of activity is indeed caused by the improvement of charge separation, the oxidation of benzyl alcohol was performed under UV light ( $\lambda < 420$  nm). UV light ( $1.46 \text{ mW cm}^{-2}$ ) was adopted to ensure that light absorption remained the same (Fig. S7†) when different catalysts were used. Thus, the influence of light absorption can be eliminated. Benzyl alcohol was oxidized to benzaldehyde without any over-oxidized products such as benzoic acid (explained in Fig. S9†). Besides, the structure of the catalysts remained unchanged after the reaction, indicating excellent stability (Fig. S10†). As shown in Fig. 5c, negligible amounts of benzaldehyde were detected without the catalyst or in the dark condition (traces 5 and 6, Fig. 5c), indicating the importance of catalysts and light. The T-HSs display a moderate photocatalytic activity (trace 4, Fig. 5c,  $12.39 \mu\text{mol}$  of product, 14 h), while the activity of PT-HSs is increased (trace 3, Fig. 5c,  $22.72 \mu\text{mol}$  of product, 14 h). By loading Pt and  $\text{MnO}_x$  simultaneously (T/P/M-HSs), the activity is further enhanced (trace 2, Fig. 5c). The highest activity ( $31.22 \mu\text{mol}$  of product, 14 h) is achieved when PTM-HSs were used (trace 1, Fig. 5c). The corresponding study on kinetics (Fig. S14†) shown in Fig. 5d exhibits the same trend (*i.e.*, activity: PTM-HSs > T/P/M-HSs > PT HSs > T-HSs).

To further confirm the enhancement of separation efficiency ( $\eta_s$ ), the apparent quantum efficiency (AQE) of PTM-HSs and T/P/M-HSs at 254 nm were determined to be 63.14% and 45.94%, respectively, which is higher than that of conventional  $\text{TiO}_2$ -based catalysts (often in the range 4.3–39%).<sup>23</sup> Because of the similar structure of the two kinds of catalysts and the same loading amount of cocatalyst, the efficiency of adsorption ( $\eta_a$ ) and surface-reaction ( $\eta_c$ ) remain the same between the catalysts (Fig. S7†). Considering the overall efficiency is determined by  $\eta_a$ ,  $\eta_s$  and  $\eta_c$  simultaneously, the enhancement of AQE can be attributed to the enhancement of  $\eta_s$ . Thus, we can quantitatively demonstrate that the spatial separation of cocatalysts indeed leads to an efficient charge separation for photocatalytic oxidation. Moreover, even under visible light ( $\lambda > 420$  nm), the electrons (generated from catalysts containing Pt and  $\text{TiO}_2$ ) still flow from  $\text{TiO}_2$  to Pt (instead of the hot electrons injected into  $\text{TiO}_2$ ), which can be proved by a probe experiment (Fig. S12†).

In order to investigate the mechanism of photocatalytic benzyl alcohol oxidation, particularly the main active species, phenol, and 4-hydroxy-2,2,6,6-tetramethylpiperidine 1-oxyl free radical (4-OH-TEMPO) were used as the scavengers of holes ( $h^+$ ) and superoxide radicals ( $\text{O}_2^-$ ), respectively. As shown in Fig. 6a, when phenol ( $h^+$  scavenger) was added into the photocatalytic system, an extremely low oxidation activity was observed, indicating that  $h^+$  plays an indispensable role in the oxidation


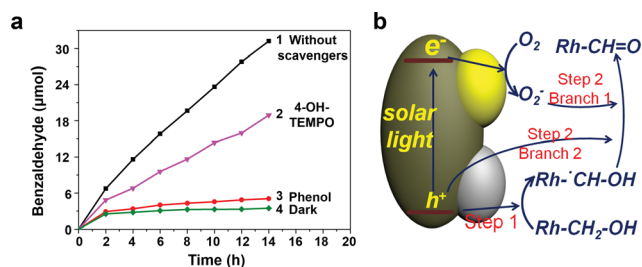


Fig. 6 (a) Effects of diverse scavengers on the photooxidation of benzyl alcohol in the presence of PTM-HSs (0.03 g). Traces 1–3 were obtained under UV light, while trace 4 was under dark conditions. (b) The proposed mechanism of photocatalytic benzyl alcohol oxidation.




process. However, when 4-OH-TEMPO ( $\text{O}_2^-$  scavenger) was added, the activity only partly decreased, indicating that  $\text{O}_2^-$  also takes part in the reaction, while it is not indispensable. These observations suggest that two photocatalytic steps might be involved. The first step primarily depends on  $h^+$ , while the second step is driven by  $h^+$  and  $\text{O}_2^-$  simultaneously. An intermediate would be formed in step 1 and be oxidized in step 2, bridging the two steps.

To determine the intermediate species, a kinetic isotope effect (KIE) study was conducted for PTM-HSs with benzyl alcohol under aerobic conditions. The KIE value was 0.78, suggesting the breaking of a C–H bond instead of an O–H bond (see ESI†). Accordingly, the intermediate was determined to be  $\text{Rh}^-\text{CH-OH}$  (Rh stands for the benzene ring). The speculated mechanism of photocatalytic benzyl alcohol oxidation is shown in Fig. 6b and eqn (1) to (5):

Step 1:



Step 2:



Upon the separation of photo-induced electrons and holes over the PTM-HSs, the holes react with benzyl alcohol molecules to form intermediate free radicals ( $\text{Rh}^-\text{CH-OH}$ ). Subsequently, some of the free radicals react with  $\text{O}_2^-$ , while others are further oxidized by holes to form the ultimate products ( $\text{Rh-CH=O}$ ). Meanwhile, oxy species finally exist as  $\text{H}_2\text{O}_2$  after a series of changes, which are discussed in detail in the ESI.†<sup>24</sup>

## Conclusions

In summary, the PTM-HS catalyst with Pt and  $\text{MnO}_x$  loaded separately onto the inner and outer surfaces of  $\text{TiO}_2$  hollow spheres was successfully synthesized for the photooxidation of





reaction. The products were analyzed by a gas chromatograph system (GC 2060, Ramiin) with a flame ionization detector (FID). A standard solution (a mixture of 5 mL of toluene, 50  $\mu$ L of benzyl alcohol, 40  $\mu$ L of benzaldehyde and 40  $\mu$ L of undecane) was used to calibrate the GC. The calibration factor (1.7) was obtained using the standard solution. Subsequently, the accurate amount of every sample was calculated using the area of every peak and the calibration factor. The correlation of peaks and products is determined by the retention time obtained from the prior analysis of pure chemicals, and further confirmed by the GC-MS analysis (Fig. S11<sup>†</sup>). To investigate the mechanism, 0.06 g of phenol and 0.06 g of 4-OH-TEMPO were added to the mixture containing 0.03 g of PTM-HSs, 5 mL of toluene (solvent), 50  $\mu$ L of benzyl alcohol (reactant) and 40  $\mu$ L of undecane (internal standard). Subsequent reactions and detections were similar to those above.

**Photocatalytic oxidation of water to O<sub>2</sub>.** The photocatalytic O<sub>2</sub> evolution reactions were carried out in a closed gas circulation and evacuation system using a 300 W xenon lamp (PerfectLight Co.) and an optical cutoff filter (PerfectLight Co.  $\lambda > 420$  nm). Normally, 0.03 g of photocatalyst was dispersed in 50 mL of 0.02 M NaIO<sub>3</sub> aqueous solution in a glass reaction cell. Before irradiation, the reaction system was thoroughly degassed by evacuation in order to drive off the air inside. The amount of evolved O<sub>2</sub> was determined by an online GC (TCD, Ar carrier). The rate of O<sub>2</sub> evolution in the initial 3 h was recorded for comparison.

**Apparent quantum efficiency (AQE).** The AQE was calculated with the following equation:  $AQE (\%) = N_e/N_p$ , where  $N_e$  and  $N_p$  are the amounts of electrons (taking part in the reaction) and incident photons, respectively. The amount of electrons is two times the amount of benzaldehyde, for every benzaldehyde molecule consumes two electrons during the reaction. The amount of benzaldehyde per unit mass and unit time was measured by a GC system after reaction under irradiation with the wavelength at  $\lambda = 254$  nm given by xenon lamp and a glass filter. The light intensity was fixed at 0.15 mW cm<sup>-2</sup> (measured by an irradiometer, UV-A, Photoelectric Instrument Factory of Beijing Normal University), and the amount of incident photons per unit time was calculated by the intensity and the energy of a single photon at  $\lambda = 254$  nm.

**Turnover number (TON).**  $TON = (\text{the number of transformed substrate molecules})/(\text{the number of active sites})$ . The number of transformed substrate molecules can be obtained by GC analysis, which has been discussed above (page 4 of ESI<sup>†</sup>). When calculating the denominator, it should be noticed that only cocatalysts (Pt and MnO<sub>x</sub>) loaded onto TiO<sub>2</sub> act as active sites, which could be illustrated by the probe experiment (Fig. S12<sup>†</sup>). The estimated TON is 4.6.

## Acknowledgements

We acknowledge the National Natural Science Foundation of China (No. 21222604, U1463205, 21525626, and 51302185), the Program for New Century Excellent Talents in University (NCET-10-0611), the Scientific Research Foundation for the Returned

Overseas Chinese Scholars (MoE), and the Program of Introducing Talents of Discipline to Universities (No. B06006) for financial support.

## Notes and references

- 1 R. Li, F. Zhang, D. Wang, J. Yang, M. Li, J. Zhu, X. Zhou, H. Han and C. Li, *Nat. Commun.*, 2013, **4**, 1432–1438.
- 2 J. Yu, L. Qi and M. Jaroniec, *J. Phys. Chem. C*, 2010, **114**, 13118–13125.
- 3 L. Duan, F. Bozoglian, S. Mandal, B. Stewart, T. Privalov, A. Llobet and L. Sun, *Nat. Chem.*, 2012, **4**, 418–423.
- 4 J. C. Colmenares and R. Luque, *Chem. Soc. Rev.*, 2014, **43**, 765–778.
- 5 J. Zhang, Y. Chen and X. Wang, *Energy Environ. Sci.*, 2015, **8**, 3092–3108.
- 6 Y. Zheng, L. Lin, B. Wang and X. Wang, *Angew. Chem., Int. Ed.*, 2015, **54**, 12868–12884.
- 7 Y. Hou, F. Zuo, A. Dagg and P. Feng, *Nano Lett.*, 2012, **12**, 6464–6473.
- 8 X. Chang, T. Wang, P. Zhang, J. Zhang, A. Li and J. Gong, *J. Am. Chem. Soc.*, 2015, **137**, 8356–8359.
- 9 J. Liu, X. Yu, Q. Liu, R. Liu, X. Shang, S. Zhang, W. Li, W. Zheng, G. Zhang, H. Cao and Z. Gu, *Appl. Catal., B*, 2014, **158–159**, 296–300.
- 10 H. Yan, J. Yang, G. Ma, G. Wu, X. Zong, Z. Lei, J. Shi and C. Li, *J. Catal.*, 2009, **266**, 165–168.
- 11 M. Yoshida, N. Gon, S. Maeda, T. Mineo, K. Nitta, K. Kato, H. Nitani, H. Abe, T. Uruga and H. Kondoh, *Chem. Lett.*, 2014, **43**, 1725–1727.
- 12 S. Obregón and G. Colón, *Appl. Catal., B*, 2014, **144**, 775–782.
- 13 J. B. Joo, M. Dahl, N. Li, F. Zaera and Y. Yin, *Energy Environ. Sci.*, 2013, **6**, 2082–2092.
- 14 W. Choi, A. Termin and M. R. Hoffmann, *J. Phys. Chem.*, 1994, **98**, 13669–13679.
- 15 A. Li, P. Zhang, X. Chang, W. Cai, T. Wang and J. Gong, *Small*, 2015, **11**, 1892–1899.
- 16 B. Kraeutler and A. J. Bard, *J. Am. Chem. Soc.*, 1978, **100**, 4317–4318.
- 17 Y. Shiraiishi, D. Tsukamoto, Y. Sugano, A. Shiro, S. Ichikawa, S. Tanaka and T. Hirai, *ACS Catal.*, 2012, **2**, 1984–1992.
- 18 W. Stöber, A. Fink and E. Bohn, *J. Colloid Interface Sci.*, 1968, **26**, 62–69.
- 19 A. L. Linsebigler, G. Lu and J. T. Yates Jr, *Chem. Rev.*, 1995, **95**, 735–758.
- 20 A. Fujishima, X. Zhang and D. A. Tryck, *Surf. Sci. Rep.*, 2008, **63**, 515–582.
- 21 J. Hou, H. Cheng, O. Takeda and H. Zhu, *Angew. Chem.*, 2015, **127**, 8600–8604.
- 22 P. Zhang, T. Wang and J. Gong, *Adv. Mater.*, 2015, **27**, 5328–5342.
- 23 S. Higashimoto, N. Kitao, N. Yoshida, T. Sakura, M. Azuma, H. Ohue and Y. Sakata, *J. Catal.*, 2009, **266**, 279–285.
- 24 J. C. Colmenares and R. Luque, *Chem. Soc. Rev.*, 2014, **43**, 765–778.

