

Cite this: *Catal. Sci. Technol.*, 2019, 9, 652

# Synthesis of a WO<sub>3</sub> photocatalyst with high photocatalytic activity and stability using synergetic internal Fe<sup>3+</sup> doping and superficial Pt loading for ethylene degradation under visible-light irradiation†

Xiaolei Liu,<sup>‡a</sup> Huishan Zhai,<sup>‡a</sup> Peng Wang,<sup>id a</sup> Qianqian Zhang,<sup>\*a</sup> Zeyan Wang,<sup>id a</sup> Yuanyuan Liu,<sup>a</sup> Ying Dai,<sup>b</sup> Baibiao Huang,<sup>id \*a</sup> Xiaoyan Qin<sup>a</sup> and Xiaoyang Zhang<sup>a</sup>

Ethylene (C<sub>2</sub>H<sub>4</sub>) is harmful for storage and fresh-keeping of fruits and vegetables. Photocatalytic technology is an effective and environmentally friendly approach for degrading ethylene. Herein, we first report the synthesis of a WO<sub>3</sub> photocatalyst with high photocatalytic activity and stability using synergetic internal Fe<sup>3+</sup> doping and superficial Pt loading for ethylene degradation under visible-light irradiation. Internal Fe<sup>3+</sup> doping not only enhances the visible-light absorption but also improves the stability to some degree due to more positive reduction potential of Fe<sup>3+</sup>/Fe<sup>2+</sup> than that of W<sup>6+</sup>/W<sup>5+</sup> and separation efficiency of the photo-generated carriers. Furthermore, the loading of Pt as a co-catalyst through the photo-reduction of H<sub>2</sub>PtCl<sub>6</sub> on the surface of Fe-doped WO<sub>3</sub> promotes the effective transfer of photo-generated electrons and reduces the photo-corrosion of WO<sub>3</sub>. Due to the synergistic effect, extremely high degradation speed can be achieved by doping 0.25 mol% Fe and loading 0.75 wt% Pt for WO<sub>3</sub>, which exceeds that of pristine WO<sub>3</sub> by about 3.3 times under visible-light irradiation. In addition, due to the excellent stability of Pt@Fe-doped WO<sub>3</sub>, it has good industrial application prospects in the field of photocatalysis.

Received 21st November 2018,  
Accepted 16th December 2018

DOI: 10.1039/c8cy02375a

rsc.li/catalysis

## 1. Introduction

Ethylene (C<sub>2</sub>H<sub>4</sub>) as a plant hormone has numerous effects on the growth, development and storage of fruits and vegetables.<sup>1</sup> During the process of growth, ethylene plays a useful role in promoting the ripening of fruits and vegetables. However, after harvesting of fruits and vegetables, ethylene can be constantly produced through respiration, which can accelerate the senescence of fruits and vegetables and is harmful for their storage and fresh-keeping.<sup>2</sup> Therefore, it is important to remove ethylene in the storage environment. Photocatalytic technology is considered as an effective and environmentally friendly approach to degrade ethylene molecules into CO<sub>2</sub> and H<sub>2</sub>O through photocatalytic oxidation.<sup>3</sup> However, due to the nonpolar nature and high bond energy of ethylene molecules, they cannot be degraded easily.<sup>4</sup> Thus, it is a great chal-

lenge to find and design efficient photocatalysts for use in photocatalytic ethylene degradation.

With respect to the photocatalytic degradation of ethylene, titanium dioxide has been proven to be the most important photocatalyst due to its high activity, long-term stability, low toxicity and low cost.<sup>5,6</sup> However, it can only respond to the ultraviolet light, which only accounts for 5% of the solar spectrum, due to its intrinsic wide band gap of about 3.2 eV.<sup>7</sup> To make good use of sunlight, semiconductor photocatalysts should have good visible-light absorption. WO<sub>3</sub> has a smaller band gap (2.5–2.8 eV) than TiO<sub>2</sub> (3.2 eV) and has many inherent advantages such as low cost, nontoxicity and high oxidation power of valence band holes.<sup>8,9</sup> In recent years, WO<sub>3</sub> has been studied as a photocatalyst in many applications such as the degradation of organic dyes, water splitting, and reduction of CO<sub>2</sub>.<sup>10–17</sup> Due to the requirement of high selectivity of photocatalysts for ethylene degradation, only some specific photocatalysts can be used to degrade ethylene. As far as we know, there has been no report on the photocatalytic ethylene degradation using WO<sub>3</sub> as the photocatalyst. Although the use of WO<sub>3</sub> has many advantages, there are still some drawbacks, which seriously restrict its performance. The first is the limited visible-light absorption; to solve this problem, doping metals is considered as a good strategy, and these metals

<sup>a</sup> State key lab of crystal materials, Shandong University, Jinan, 250100, China.

E-mail: qianqianzhang@sdu.edu.cn, bbhuang@sdu.edu.cn

<sup>b</sup> School of physics, Shandong University, Jinan, 250100, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8cy02375a

‡ These authors contributed equally to this work.

include Ti, Cu, Mo and Fe.<sup>18–21</sup> The second is that WO<sub>3</sub> is easily photo-corroded due to self-reduction of W<sup>6+</sup>, which is disadvantageous for photocatalytic activity.

In this study, we first report the synthesis of a WO<sub>3</sub> photocatalyst with high photocatalytic activity and stability using synergetic internal Fe<sup>3+</sup> doping and superficial Pt loading for ethylene degradation under visible-light irradiation. The optimal calcination temperature for WO<sub>2.72</sub> to produce WO<sub>3</sub>, the optimal doping amount of Fe<sup>3+</sup> and loading amount of Pt are studied in our experiment systematically. Internal Fe<sup>3+</sup> doping not only enhances the visible-light absorption but also promotes the stability to some degree due to more positive reduction potential of Fe<sup>3+</sup>/Fe<sup>2+</sup> than that of W<sup>6+</sup>/W<sup>5+</sup>. During the photocatalytic reaction, the photo-generated electrons are more easily captured by Fe<sup>3+</sup> and are converted to Fe<sup>2+</sup>, which can avoid the photo-corrosion of WO<sub>3</sub> effectively and promote the separation of photo-generated carriers. Furthermore, the loading of Pt as a co-catalyst through the photo-reduction of H<sub>2</sub>PtCl<sub>6</sub> on the surface of Fe-doped WO<sub>3</sub> promotes the effective transfer of photo-generated electrons and reduces the photo-corrosion of WO<sub>3</sub>. The synergistic effect of internal Fe<sup>3+</sup> doping and superficial Pt loading can realize the best photocatalytic activity for the degradation of ethylene under visible-light irradiation. The synergetic mechanism can be expressed clearly using a metaphor: the photo-generated electrons are water, the internal doping of Fe<sup>3+</sup> can be represented by a water reservoir and superficial Pt co-catalyst functions as a water pump. Thus, the photo-generated electrons and holes can be separated efficiently. After a certain time, the water reservoir should be released. Calcination is an effective way to convert Fe<sup>2+</sup> back to Fe<sup>3+</sup>; thus, the photocatalyst can realize excellent recyclability. The effective synergistic effect can provide a good model for other photocatalytic systems.

## 2. Experimental

### 2.1 Material synthesis

**2.1.1 Synthesis of WO<sub>2.72</sub> and WO<sub>3</sub>.** WO<sub>2.72</sub> was synthesized according to a previously reported method.<sup>18</sup> Briefly, 2 g of WCl<sub>6</sub> was added into 80 ml of absolute ethanol, and a clear and bright yellow solution was formed with vigorous stirring. The solution was then transferred into a 100 mL-Teflon-lined autoclave and heated at 160 °C for 24 h. When cooled to room temperature, the blue product was filtered, washed with ethanol and distilled water several times and then dried in air at 60 °C overnight. In order to determine the optimal calcination temperature for the synthesis of WO<sub>3</sub>, the blue WO<sub>2.72</sub> powder was calcined at 300, 350, 400, 450, and 500 °C for 1.5 hours in air with a heating rate of 10 °C min<sup>-1</sup>.

**2.1.2 Synthesis of Fe-doped WO<sub>3</sub>.** The Fe-doped WO<sub>3</sub> was synthesized by a similar method except that a different amount of iron(III) nitrate nonahydrate (Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O) was added. The theoretical contents of Fe in WO<sub>3</sub> were 0.1, 0.25, 0.5, 0.75 and 1.0 mol%. Then, the as-prepared samples were

calcined at 450 °C in air for 1.5 hours to obtain the Fe-doped WO<sub>3</sub>.

**2.1.3 Synthesis of Pt@Fe-WO<sub>3</sub>.** Pt@Fe-WO<sub>3</sub> was synthesized *via* the photo-reduction method. First, 0.5 g of 0.25 mol% Fe-doped WO<sub>2.72</sub> was dispersed in 100 mL distilled water by sonication for 5 min. Then, a certain volume of H<sub>2</sub>PtCl<sub>6</sub> (0.0772 M) was added to the above suspension. After stirring for 30 minutes, 1 mL methanol was added. The system was irradiated by full spectrum light for 30 minutes. The products were filtrated and washed with water. After drying at 60 °C, the products were calcined at 450 °C in air for 1.5 hours.

### 2.2 Material characterization

XRD was characterized on a Bruker AXS D8 diffractometer equipped with Cu K $\alpha$  excitation. UV-vis DRS of the products was conducted using a Shimadzu UV 2550 spectrophotometer equipped with an integrating sphere. Morphology was observed by a field emission scanning electron microscope (SEM) (Hitachi S-4800) equipped with an energy dispersive spectrometer (EDS). XPS measurements were obtained using a Thermo Fisher Scientific Escalab 250 spectrometer, and the peak positions of various elements were calibrated by C 1s (284.8 eV). The PL curves using 350 nm as the excitation wavelength were surveyed by a Hitachi F-4500 fluorescence spectrophotometer. Photoelectrochemical measurements with a three-electrode system were conducted using a Princeton Applied Research EG&G 263A electrochemical workstation. The platinum sheet served as the counter electrode; Ag/AgCl served as the reference electrode, and catalyst-covered FTO glass served as the working electrode. The electrolyte solution was 0.5 M Na<sub>2</sub>SO<sub>4</sub>. A 300 W Xe-arc lamp equipped with an AM 1.5 cut-off filter was used as the light source.

### 2.3 Photocatalytic test

The photocatalytic ethylene degradation experiment was carried out in a special reactor with a volume of 320 mL; 0.4 g of photocatalyst was sprinkled uniformly at the bottom of the reactor, and the reactor was sealed by a silicone rubber stopper. Then, 0.4 mL of high-purity ethylene gas was injected into the reactor, and the reaction temperature of the system was maintained at 15 °C with cooling water. The initial concentration of ethylene (C<sub>2</sub>H<sub>4</sub>) was 1250 ppm. A 300 W Xe lamp with a 420 nm cut-off filter was used to provide the visible light. Prior to irradiation, the system was magnetically stirred in the dark for 2 h to establish an adsorption-desorption equilibrium of the gas with the samples. When a balance was reached, the photocatalytic test began. First, 60  $\mu$ L of the gas mixture was sampled from the reaction system at a certain time interval and was analyzed by an online gas chromatograph (Shimadzu GC-2014C) equipped with a thermal conductivity detector (TCD). A blank test was also conducted without photocatalyst to prove that the degradation of ethylene was entirely caused by the photocatalytic reaction. The

degradation percentage is expressed as  $C/C_0$ , where  $C_0$  is the initial concentration of ethylene and  $C$  represents the corresponding concentration at a certain sampling time. The stability was tested as follows: after each ethylene oxidation reaction, the photocatalyst was collected and calcined at 450 °C for 0.5 hours to remove possible residuary organics. Then, the regenerated product was employed to conduct another round of ethylene degradation test under the same conditions.

### 3. Results and discussion

#### 3.1 X-ray diffraction study of the samples

The crystallographic structures of the samples were characterized by X-ray diffraction (XRD). The XRD spectra of untreated  $WO_{2.72}$  and  $WO_{2.72}$  calcined at different temperatures are shown in Fig. 1. As can be seen, the crystallinity of all products improved after calcination. The diffraction peaks gradually transformed from  $WO_{2.72}$  (JCPDS no. 36-101) to  $WO_3$  (JCPDS no. 43-1035) with increase in calcination temperature. When the calcination temperature reached 400 °C, the sample entirely transformed into  $WO_3$ . Therefore, the calcination temperature is a very important factor for the formation of  $WO_3$  from  $WO_{2.72}$ .

As shown in Fig. 2a, after calcination at 450 °C, all the diffraction peaks of the as-prepared samples are nearly similar to that of pure  $WO_3$ . With the increase in Fe content, no apparent diffraction peaks of iron oxides or other impurity phases can be detected, illustrating that  $Fe^{3+}$  ions were doped into the crystal lattice of  $WO_3$ .<sup>21</sup> However, from the enlarged peaks in Fig. 2b, we infer that the peaks in the Fe-doped products display apparent shifts compared to that of original  $WO_3$ . With the increase in Fe content, the diffraction peaks gradually shifted to a small angle. Because the radius of  $Fe^{3+}$  (0.64 Å) is larger than the radius of  $W^{6+}$  (0.62 Å), slight lattice distortion of  $WO_3$  was observed. According to the Bragg's law, the diffraction angle will become smaller due to larger lattice spacing, which can explain the result of the peak offset. This phenomenon further indicates that the  $Fe^{3+}$  ions were doped into the crystal lattice of  $WO_3$  successfully. More-

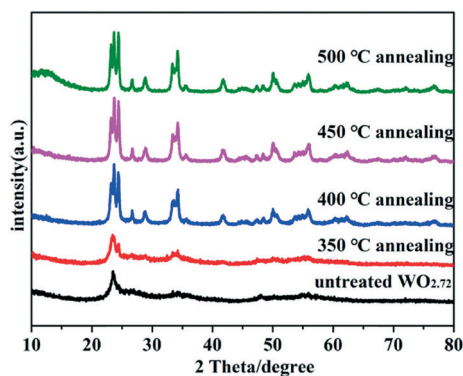


Fig. 1 XRD patterns of untreated  $WO_{2.72}$  and  $WO_{2.72}$  calcined at different temperatures.

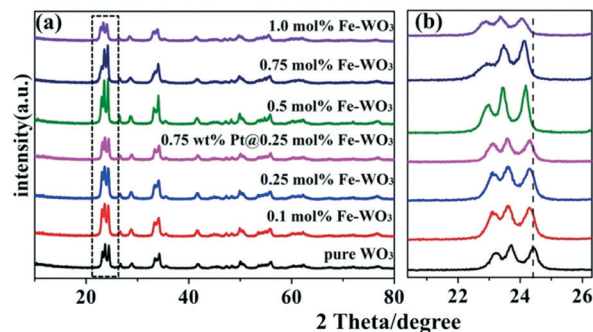


Fig. 2 The XRD spectra (a) and the enlarged XRD spectra (b) of the pure  $WO_3$ , Fe-doped  $WO_3$  and Pt@Fe- $WO_3$  samples.

over, the XRD peaks of 0.75 wt% Pt@0.25 mol% Fe- $WO_3$  were similar to those of 0.25 mol% Fe- $WO_3$ , and no clear peaks of Pt were detected, which might be caused by the low amount and high dispersion of Pt nanoparticles.

#### 3.2 UV-vis spectroscopy

The UV-vis diffuse reflectance spectra of bare  $WO_3$ , Fe-doped  $WO_3$  and Pt@Fe- $WO_3$  samples are shown in Fig. 3. As can be seen, bare  $WO_3$  displays a sharp absorption edge at around 470 nm and a corresponding band gap energy of about 2.64 eV, which is consistent with previous results (2.5–2.8 eV).<sup>8</sup> All products exhibited absorption in both UV and visible-light regions. Due to the low doping amount of  $Fe^{3+}$ , the absorption edge only has a small red shift. Based on the enlarged view inserted in Fig. 3, we observe that the red shift of the absorption increases gradually with the increase in  $Fe^{3+}$  doping from 0.1 to 1.0%. The enhanced visible-light absorption of Fe-doped  $WO_3$  is beneficial for the photocatalytic reaction, and it also confirms that  $Fe^{3+}$  was indeed doped into the lattice of  $WO_3$ . After photo-reduction of  $H_2PtCl_6$ , the light absorption increased in the 500–800 nm region, which was ascribed to the loading of Pt nanoparticles on the surface.

#### 3.3 Morphology and structure of nanostructures

The morphologies of the obtained samples were studied by SEM (Fig. 4). It can be observed that the  $WO_{2.72}$  product possesses uniform urchin-like hierarchical structures with sizes

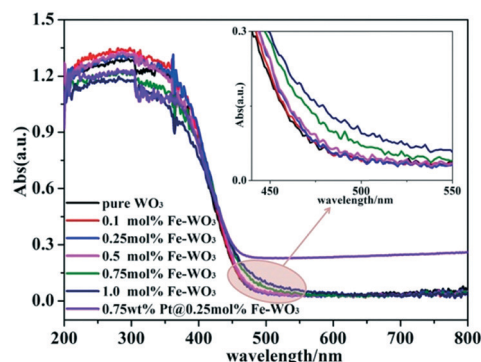


Fig. 3 UV-vis diffuse absorption spectra of the as-prepared samples.



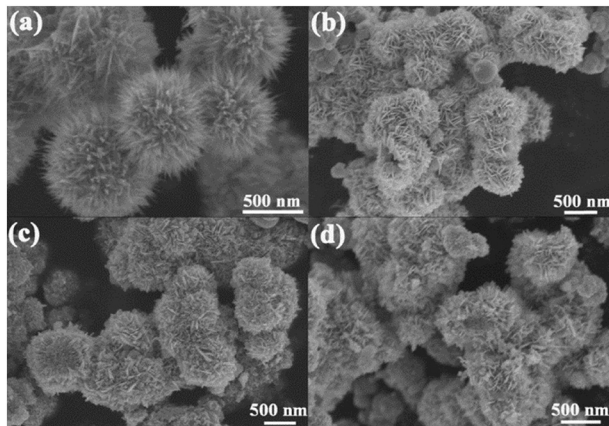


Fig. 4 SEM images of (a) bare  $\text{WO}_{2.72}$ , (b) pure  $\text{WO}_3$  ( $\text{WO}_{2.72}$  calcined at  $450\text{ }^\circ\text{C}$  for 1.5 h), (c) 0.25 mol% Fe-doped  $\text{WO}_3$  (0.25 mol% Fe-doped  $\text{WO}_{2.72}$  calcined at  $450\text{ }^\circ\text{C}$  for 1.5 h), (d) 0.75 wt% Pt@0.25 mol% Fe- $\text{WO}_3$  after 9 time photocatalytic degradation experiments.

ranging from 600 to 800 nm (Fig. 4a), which is consistent with the results from a previous report.<sup>22</sup> The morphology of the as-synthesized urchin-like  $\text{WO}_{2.72}$  architectures calcined at  $450\text{ }^\circ\text{C}$  is shown in Fig. 4b. After calcination, the original urchin-like hierarchical structures transformed into hierarchical microspheres consisting of nanoflakes due to recrystallization. The detailed morphologies of the as-synthesized urchin-like  $\text{WO}_{2.72}$  architectures calcined at different temperatures are shown in Fig. S1.† As the temperature increased, the transformation process started gradually and the thickness of the nanoflakes increased. Combined with the result of XRD, we infer that the urchin-like  $\text{WO}_{2.72}$  has been completely converted to  $\text{WO}_3$  at  $400\text{ }^\circ\text{C}$ . As shown in Fig. 4c, the morphology of 0.25 mol% Fe-doped  $\text{WO}_3$  is also composed of nanosheet arrays but with slight disorder compared with the morphology of un-doped  $\text{WO}_3$ . In addition, it should be noted that 0.75 wt% Pt@0.25 mol% Fe- $\text{WO}_3$  exhibits no significant morphological change after 9 time consecutive photocatalytic degradation experiments (Fig. 4d), indicating that the loading of Pt by photo-reduction and calcination at  $450\text{ }^\circ\text{C}$  for 0.5 h after every cycle experiment have almost no influence on the morphology.

Fig. 5 displays the EDS and mapping analysis of the 0.75 wt% Pt@0.25 mol% Fe- $\text{WO}_3$  sample. In Fig. 5a, W, O, Fe and

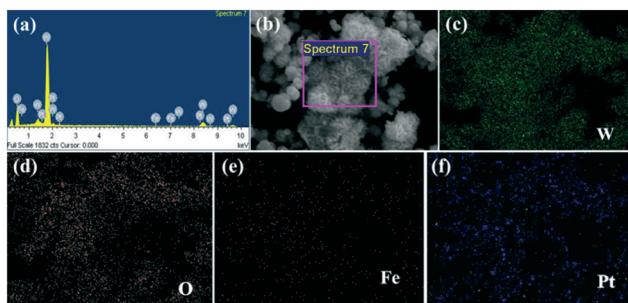


Fig. 5 (a) EDS, (b) SEM and (c–f) mapping analysis of 0.75 wt% Pt@0.25 mol% Fe- $\text{WO}_3$  sample.

Pt can be detected by the EDS measurements. To intuitively observe the elemental distribution, EDS mapping was carried out. The detailed results can be seen in Fig. 5b–f. These results further prove the successful Fe doping and Pt loading in the  $\text{WO}_3$  system.

### 3.4 X-ray photoelectron spectroscopy study

To assess the surface chemical status of Fe-doped  $\text{WO}_3$  before and after irradiation, X-ray photoelectron spectroscopy (XPS) was carried out. Fig. 6a shows the full XPS spectra of bare  $\text{WO}_3$  and Fe-doped  $\text{WO}_3$  before and after irradiation; the corresponding peaks of O 1s, C 1s and W 4f can be observed clearly. The peak of C 1s located at 284.8 eV is used to calibrate the peak positions. Due to the small doping amount of Fe, the XPS peak of  $\text{Fe}^{3+}$  2p cannot be easily seen in Fig. 6a. From Fig. 6b and c, we can see that the peaks of W 4f (35.28 eV for W 4f<sup>7/2</sup> and 37.4 eV for W 4f<sup>5/2</sup>) and O 1s (530.3 eV) for Fe-doped  $\text{WO}_3$  before irradiation exhibit a slightly negative shift relative to the peaks of W 4f (35.8 eV for W 4f<sup>7/2</sup> and 37.9 eV for W 4f<sup>5/2</sup>) and O 1s (530.64 eV) for un-doped  $\text{WO}_3$ . From the high-resolution Fe 2p spectrum (Fig. 6d), we observe that the two small peaks located at 715.35 eV and 724.86 eV, corresponding to Fe 2p<sup>3/2</sup> and Fe 2p<sup>1/2</sup>, exhibit slightly positive shifts compared to that of  $\text{Fe}_2\text{O}_3$  reported previously (710.7 eV for Fe 2p<sup>3/2</sup> and 724.3 eV for Fe 2p<sup>1/2</sup>).<sup>23</sup> The shift of the peaks in the XPS spectrum is due to different electronegativities of W and Fe; the electronegativity of W is relatively smaller than that of Fe.<sup>24,25</sup> When  $\text{Fe}^{3+}$  is doped into  $\text{WO}_3$ ,  $\text{Fe}^{3+}$  replaces a part of  $\text{W}^{6+}$  to form an Fe–O–W bond. Compared with the Fe–O–Fe bonding in  $\text{Fe}_2\text{O}_3$ , the bonding between Fe and O is slightly enhanced in the Fe–O–W bond, and the bonding between W and O is slightly reduced compared with that in W–O–W. Therefore, the peak of Fe 2p has a slightly positive shift, and the peaks of W 4f and

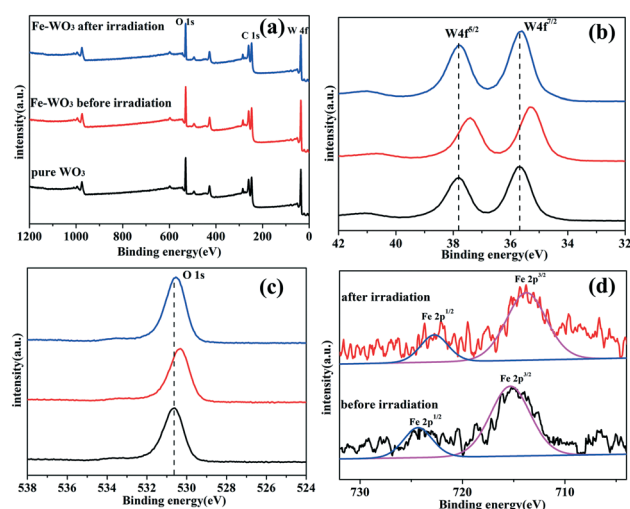


Fig. 6 (a) XPS survey spectra and (b and c) high-resolution XPS spectra of W 4f and O 1s for pure  $\text{WO}_3$  and 0.25 mol% Fe-doped  $\text{WO}_3$  before and after irradiation, (d) high-resolution XPS spectra of Fe 2p for 0.25 mol% Fe-doped  $\text{WO}_3$  before and after irradiation.

O 1s have slightly negative shifts. After the photocatalytic reaction, the binding energy positions of Fe 2p exhibit slightly negative shifts (713.74 eV for Fe 2p<sup>3/2</sup> and 722.77 eV for Fe 2p<sup>1/2</sup>); the binding energy positions of W 4f (35.62 eV for W 4f<sup>7/2</sup> and 37.78 eV for W 4f<sup>5/2</sup>) and O 1s (530.6 eV) for Fe-doped WO<sub>3</sub> after irradiation exhibit a slightly positive shift relative to that of Fe-doped WO<sub>3</sub> before irradiation. The binding energy positions of W 4f and O 1s for Fe-doped WO<sub>3</sub> after the photocatalytic reaction are almost the same as those of un-doped WO<sub>3</sub>. According to the variation in binding energy positions, we conclude that the reduction potential of Fe<sup>3+</sup>/Fe<sup>2+</sup> is more positive than that of W<sup>6+</sup>/W<sup>5+</sup>; therefore, Fe<sup>3+</sup> can more easily capture photo-generated electrons to generate Fe<sup>2+</sup> during the photocatalytic reaction, which results in decrease in the electronegativity. Therefore, the bonding between O and Fe is weakened and the bonding between O and W is strengthened in Fe–O–W. Simultaneously, the presence of Fe<sup>3+</sup> can prevent the photo-corrosion of WO<sub>3</sub> (W<sup>6+</sup> changes into W<sup>5+</sup> by photo-generated electrons), which is beneficial for the photocatalytic reaction.

### 3.5 Photocatalytic activity

The photocatalytic activities of WO<sub>3</sub>, Fe-doped WO<sub>3</sub> and Pt@Fe-doped WO<sub>3</sub> were evaluated by performing photocatalytic ethylene degradation under visible-light irradiation. To obtain the optimal calcination temperature for WO<sub>2.72</sub> to determine the optimal photocatalytic performance for initial WO<sub>3</sub>, multi-group degradation experiments were performed under the irradiation of full spectrum light. The detailed results can be seen in the ESI† (Fig. S2a). Among the studied samples, the sample calcined at 450 °C exhibited optimal photocatalytic ethylene degradation performance; thus, we chose 450 °C as the optimal annealing temperature. In addition, the optimal doping amount of Fe<sup>3+</sup> ions was also chosen in our experiment, and the detailed result can be seen in the ESI† (Fig. S2b). When the doping amount of Fe<sup>3+</sup> ions reached 0.25 mol%, the sample exhibited optimal photocatalytic performance under irradiation with full spectrum light. More doping amount caused decrease in the photocatalytic activity due to introduction of too much recombination centers.<sup>26,27</sup> The photocatalytic activity can be further improved by loading of Pt as a co-catalyst, and the optimal loading amount of Pt is 0.75 wt%; the detailed result can be seen in ESI† (Fig. S2c). After all the optimal parameters were chosen, we performed the photocatalytic degradation of ethylene using no photocatalyst, pure WO<sub>3</sub>, 0.25 mol% Fe–WO<sub>3</sub> and 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> under visible-light irradiation. The detailed results are shown in Fig. 7a. Without a photocatalyst, the concentration of ethylene was almost invariable, which proved that the degradation of ethylene is entirely caused by the photocatalytic reaction. After Fe<sup>3+</sup> ions were doped into WO<sub>3</sub>, the photocatalytic activity improved almost 2 times than that of pure WO<sub>3</sub>. To further improve the photocatalytic activity, Pt as a co-catalyst was loaded on the 0.25 mol% Fe–WO<sub>3</sub> sample through photo-reduction. The

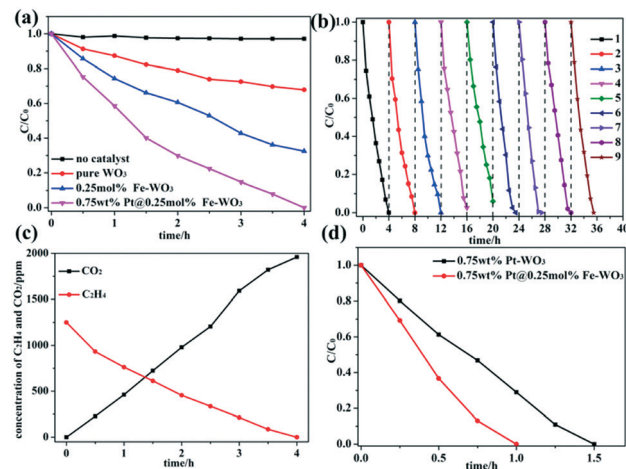


Fig. 7 (a) Photocatalytic degradation of ethylene using no catalyst, pure WO<sub>3</sub>, 0.25 mol% Fe–WO<sub>3</sub> and 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> under visible-light irradiation; (b) the photocatalytic stability experiment of 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> under visible-light irradiation; (c) photocatalytic process of C<sub>2</sub>H<sub>4</sub> degradation and CO<sub>2</sub> generation for 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> under visible-light irradiation and (d) the comparison of 0.75 wt% Pt–WO<sub>3</sub> and 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> in photocatalytic ethylene degradation under full spectrum light irradiation.

0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> sample exhibited the optimal photocatalytic activity and could degrade all of the ethylene in four hours under irradiation of visible light. From Fig. 7c, we can see that the concentration of CO<sub>2</sub> increased gradually during the process of photocatalytic degradation of C<sub>2</sub>H<sub>4</sub>, and the results illustrate that 80% C<sub>2</sub>H<sub>4</sub> can be completely degraded to CO<sub>2</sub>. The other partially oxidized intermediate species contain mainly CO and a small amount of formaldehyde. Stability is a very important criterion for the practical application of a photocatalyst. The recyclability of the photocatalyst was studied by performing consecutive degradation experiments under irradiation of visible light. After each cycle, the sample was collected and calcined at 450 °C for 0.5 hour to remove possible residuary organics. The result of the cycle experiment can be seen in Fig. 7b; the sample still maintained the initial photocatalytic activity after nine cycles, revealing that the photocatalyst has excellent recyclability. To prove the important effect of Fe doping, a contrast experiment was carried out using 0.75 wt% Pt–WO<sub>3</sub> and 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> as photocatalysts under irradiation with full spectrum light. The detailed results can be seen in Fig. 7d. The results show that the photocatalytic activity of 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> is superior to that of 0.75 wt% Pt–WO<sub>3</sub>, thereby illustrating that Fe doping in the system plays an important role during the photocatalytic degradation. The photocatalytic degradation activity of 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> sample was compared with that of other photocatalysts such as Pt–TiO<sub>2</sub>, Ag–ZnO, AuAg–ZnO, BiVO<sub>4</sub>/P25, and In<sub>2</sub>O<sub>3</sub>–Ag–Ag<sub>3</sub>PO<sub>4</sub>; the detailed information can be found in Table S1 (ESI†). Under visible-light irradiation, the photocatalytic C<sub>2</sub>H<sub>4</sub> degradation activity of 0.75 wt% Pt@0.25 mol% Fe–WO<sub>3</sub> was better than those of BiVO<sub>4</sub>/P25

and  $\text{In}_2\text{O}_3\text{-Ag-Ag}_3\text{PO}_4$ . Under full light irradiation, its activity was no less than those of  $\text{Ag-ZnO}$  and  $\text{AuAg-ZnO}$ , but it was poorer than that of  $\text{Pt-TiO}_2$ . This proves that  $\text{Pt@Fe-doped WO}_3$  has a good application prospect.

### 3.6 Photoelectrochemical measurement and photoluminescence spectra

Photoelectrochemical tests and PL spectra are usually used to determine the separation ability of photo-excited carriers.<sup>28–30</sup>

Fig. 8a shows the results of the transient photocurrent response of pure  $\text{WO}_3$  and 0.25 mol%  $\text{Fe-WO}_3$  under AM 1.5 light irradiation in 0.5 M  $\text{Na}_2\text{SO}_4$  aqueous solution at a bias potential of 1.23 V. Clearly, the 0.25 mol%  $\text{Fe-WO}_3$  sample shows larger photocurrent density than pure  $\text{WO}_3$  at the same bias potential, suggesting that the photo-generated electron-hole pairs in  $\text{Fe-doped WO}_3$  can be easily separated compared to those in pure  $\text{WO}_3$ . Fig. 8b displays the PL intensity of pristine  $\text{WO}_3$ , 0.25 mol%  $\text{Fe-WO}_3$  and 0.75 wt%  $\text{Pt@0.25 mol\% Fe-WO}_3$ . As can be seen, the PL intensity of 0.25 mol%  $\text{Fe-WO}_3$  is lower than that of pristine  $\text{WO}_3$ , demonstrating a lower electron-hole recombination rate for 0.25 mol%  $\text{Fe-WO}_3$  compared with that of pristine  $\text{WO}_3$ . This result is consistent with the result of the transient photocurrent response. Furthermore, the PL intensity further decreased when 0.75 wt% Pt was loaded onto 0.25 mol%  $\text{Fe-WO}_3$ , indicating that the recombination rate of electrons and holes further decreased. These results are in good agreement with photocatalytic activity.

### 3.7 Photocatalytic mechanism

From all the above results, the possible photocatalytic mechanism is shown in Fig. 9. When the photocatalyst is irradiated using visible light ( $\lambda \geq 420$  nm),  $\text{WO}_3$  absorbs photons to produce photo-generated electrons and holes. In previous studies, it has been reported that  $\text{Fe}^{3+}$  usually acts as an electron acceptor during the photocatalytic  $\text{O}_2$  production for  $\text{WO}_3$ .<sup>31,32</sup> Also, according to the XPS results, we can conclude that  $\text{Fe}^{3+}$  more easily captures photo-generated electrons to generate  $\text{Fe}^{2+}$  during the photocatalytic reaction due to more positive reduction potential of  $\text{Fe}^{3+}/\text{Fe}^{2+}$  (0.771 V) than that of  $\text{W}^{6+}/\text{W}^{5+}$ .<sup>33</sup> This can avoid the photo-corrosion of  $\text{WO}_3$  effectively and decrease the recombination of photo-generated car-

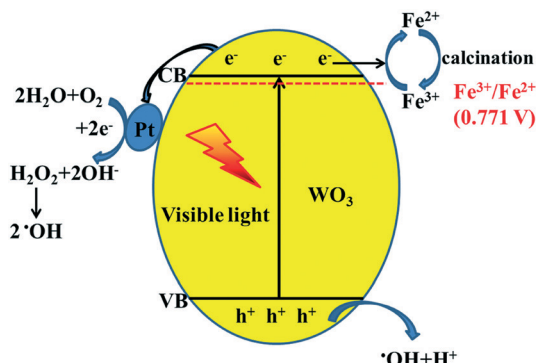


Fig. 9 Proposed schematic diagram of charge transfer in the  $\text{Pt@Fe-WO}_3$  system under visible-light irradiation.

riers. Furthermore, Pt as a co-catalyst was loaded onto the surface of  $\text{Fe-doped WO}_3$  through photo-reduction of  $\text{H}_2\text{PtCl}_6$ . The work function of  $\text{WO}_3$  (5.7 eV) is larger than that of Pt (5.1 eV); when they are in contact with each other, the electrons migrate from Pt to the conduction band of  $\text{WO}_3$  to achieve equilibration of the Fermi level.<sup>34</sup> The formation of the built-in electric field can promote the effective transfer of photo-generated electrons to Pt sites under visible irradiation, which is beneficial for the separation of photo-generated carriers and the reduction of the photo-corrosion of  $\text{WO}_3$ . Due to the low CB level of  $\text{WO}_3$ , the process of the single-electron reduction of oxygen cannot proceed. The accumulated electrons on the Pt particles are then used for the multi-electron reduction of oxygen molecules to form  $\text{H}_2\text{O}_2$  and then for further production of hydroxyl radicals ( $\cdot\text{OH}$ ); loading of Pt can accelerate the reaction of the photo-excited electrons with  $\text{O}_2$ .<sup>35,36</sup> The photo-generated holes with high oxidation potential react with the surface-adsorbed  $\text{H}_2\text{O}$  to produce hydroxyl radicals. The hydroxyl radicals as extremely strong oxidants can degrade the  $\text{C}_2\text{H}_4$  molecules effectively. The synergistic effect of internal  $\text{Fe}^{3+}$  doping and superficial Pt loading can be expressed by a metaphor: the photo-generated electrons are water, the internal doping of  $\text{Fe}^{3+}$  functions as a water reservoir, and the superficial Pt co-catalyst functions as a water pump. After a certain time, the water reservoir should be released. Calcination is an effective way to convert  $\text{Fe}^{2+}$  back to  $\text{Fe}^{3+}$ , and the photocatalyst can realize excellent recyclability.

## 4. Conclusions

We first report the synthesis of  $\text{WO}_3$  nanostructures with high photocatalytic activity and stability using synergetic internal  $\text{Fe}^{3+}$  doping and superficial Pt loading for ethylene degradation under visible-light irradiation. The optimal doping amount of  $\text{Fe}^{3+}$  is 0.25 mol% and the optimal loading amount of Pt is 0.75 wt%; the synergetic modification can result in about 3.3-fold improvement in the degradation rate than that of pure  $\text{WO}_3$  in photocatalytic ethylene degradation. The doped  $\text{Fe}^{3+}$  and loaded Pt particles can capture photo-generated electrons to reduce the recombination of

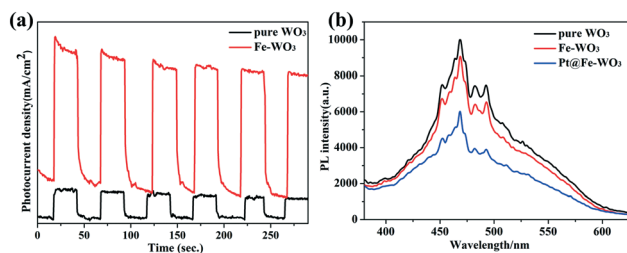


Fig. 8 (a) Photocurrent curves of pure  $\text{WO}_3$  and 0.25 mol%  $\text{Fe-doped WO}_3$ ; (b) PL spectra of pure  $\text{WO}_3$ , 0.25 mol%  $\text{Fe-doped WO}_3$  and 0.75 wt%  $\text{Pt@0.25 mol\% Fe-WO}_3$ .



photo-generated carriers and protect  $\text{WO}_3$  from photo-corrosion. This photocatalyst shows excellent photocatalytic degradation stability, revealing that it has an excellent application prospect.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was financially supported by a research grant from the National Natural Science Foundation of China (No. 51602179, 21333006, 21573135 and 11374190), and the National Basic Research Program of China (973 Program, No. 2013CB632401), Recruitment Program for Young Professionals, China and Taishan Scholar Foundation of Shandong Province, China.

## Notes and references

- M. E. Saltveit, *Postharvest Biol. Technol.*, 1999, **15**(3), 279–292.
- X. L. Song, Y. Y. Li, Z. D. Wei, S. Y. Ye and D. D. Dionysiou, *Chem. Eng. J.*, 2017, **314**, 443–452.
- N. Keller, M. N. Ducamp, D. Robert and V. Keller, *Chem. Rev.*, 2013, **113**, 5029–5070.
- J. A. Labinger and J. E. Bercaw, *Nature*, 2002, **417**, 507–514.
- M. R. Hoffmann, S. T. Martin, W. Choi and D. W. Bahnemann, *Chem. Rev.*, 1995, **95**, 69–96.
- S. G. Kumar and K. S. R. K. Rao, *Appl. Surf. Sci.*, 2017, **391**, 124–148.
- P. Wang, B. Huang, X. Qin, X. Zhang, Y. Dai and M. Whangbo, *Inorg. Chem.*, 2009, **48**(22), 10697–10702.
- C. Brian, B. Marsen, E. Miller, Y. Yan and B. To, *J. Phys. Chem. C*, 2008, **112**(13), 5213–5220.
- W. Morales, M. Cason, O. Aina, N. R. de Tacconi and K. Rajeshwar, *J. Am. Chem. Soc.*, 2008, **130**(20), 6318–6319.
- T. Gunji, A. J. Jeevagan, M. Hashimoto, T. Nozawa, T. Tanabe, S. Kaneko, M. Miyauchi and F. Matsumoto, *Appl. Catal., B*, 2016, **181**, 475–480.
- D. P. DePuccio, P. Botella, B. O. Rourke and C. C. Landry, *ACS Appl. Mater. Interfaces*, 2015, **7**(3), 1987–1996.
- A. Tanaka, K. Hashimoto and H. Kominami, *J. Am. Chem. Soc.*, 2014, **136**(2), 586–589.
- J. Jin, J. Yu, D. Guo, C. Cui and W. Ho, *Small*, 2015, **11**(39), 5262–5271.
- W. L. Yu, J. X. Chen, T. T. Shang, L. F. Chen, L. Gu and T. Y. Peng, *Appl. Catal., B*, 2017, **219**, 693–704.
- F. G. Wang, C. D. Valentin and G. Pacchioni, *ChemCatChem*, 2012, **4**, 476–478.
- L. F. Li, X. L. Zhao, D. L. Pan and G. S. Li, *Chin. J. Catal.*, 2017, **38**, 2132–2140.
- J. G. Wang, Z. M. Chen, G. J. Zhai and Y. Men, *Appl. Surf. Sci.*, 2018, **462**, 760–771.
- C. Feng, S. Wang and B. Geng, *Nanoscale*, 2011, **3**(9), 3695–3699.
- H. Irie, S. Miura, K. Kamiya and K. Hashimoto, *Chem. Phys. Lett.*, 2008, **457**, 202–205.
- N. Li, H. Teng, L. Zhang, J. Zhou and M. Liu, *RSC Adv.*, 2015, **5**(115), 95394–95400.
- H. Song, Y. G. Li, Z. R. Lou, M. Xiao, L. Hu, Z. Z. Ye and L. P. Zhu, *Appl. Catal., B*, 2015, **166**, 112–120.
- G. Xi, J. Ye, Q. Ma, N. Su, H. Bai and C. Wang, *J. Am. Chem. Soc.*, 2012, **134**(15), 6508–6511.
- T. Yamashita and P. Hayes, *Appl. Surf. Sci.*, 2008, **254**, 2441–2449.
- M. Xu, P. M. Da, H. Y. Wu, D. Y. Zhao and G. F. Zheng, *Nano Lett.*, 2012, **12**, 1503.
- T. Zhang, Z. Zhu, H. Chen, Y. Bai, S. Xiao, X. Zheng, Q. Xue and S. Yang, *Nanoscale*, 2015, **7**, 2933–2940.
- Y. H. Lu, W. H. Lin, C. Y. Yang, Y. H. Chiu, Y. C. Pu, M. H. Lee, Y. C. Tseng and Y. J. Hsu, *Nanoscale*, 2014, **6**, 8796–8803.
- R. R. Prabhakar, N. Mathews, K. B. Jinesh, K. Karthik, S. S. Pramana, B. Varghese, C. H. Sow and S. Mhaisalkar, *J. Mater. Chem.*, 2012, **22**, 9678–9683.
- X. L. Liu, Q. Li, P. Wang, Y. Z. Liu, B. B. Huang, E. A. Rozhkova, Q. Q. Zhang, Z. Y. Wang, Y. Dai and J. Lu, *Chem. Eng. J.*, 2018, **337**, 480–487.
- X. L. Liu, P. Wang, H. S. Zhai, Q. Q. Zhang, B. B. Huang, Z. Y. Wang, Y. Y. Liu, X. Y. Qin and X. Y. Zhang, *Appl. Catal., B*, 2018, **232**, 521–530.
- Y. Q. Wu, P. Wang, Z. H. Guan, J. X. Liu, Z. Y. Wang, Z. K. Zheng, S. Y. Jin, Y. Dai, M. H. Whangbo and B. B. Huang, *ACS Catal.*, 2018, **8**, 10349–10357.
- G. R. Bamwenda, T. Uesigi, Y. Abe, K. Sayama and H. Arakawa, *Appl. Catal., A*, 2001, **205**(1–2), 117–128.
- O. Tomita, S. Nitta, Y. Matsuta, S. Hosokawa, M. Higashi and R. Abe, *Chem. Lett.*, 2016, **46**(2), 221–224.
- H. G. Yu, H. Irie, Y. Shimodaira, Y. Hosogi, Y. Kuroda, M. Miyauchi and K. Hashimoto, *J. Phys. Chem. C*, 2010, **114**, 16481–16487.
- Q. Arutanti, A. Nandiyanto, T. Ogi, T. Kim and K. Okuyama, *ACS Appl. Mater. Interfaces*, 2015, **7**(5), 3009–3017.
- S. M. Sun, W. Z. Wang, S. Z. Zeng, M. Shang and L. Zhang, *J. Hazard. Mater.*, 2010, **178**(1–3), 427–433.
- R. Abe, H. Takami, N. Murakami and B. Ohtani, *J. Am. Chem. Soc.*, 2008, **130**, 7780–7781.